

Cite this: *RSC Adv.*, 2018, 8, 21933

Enhancement of dissipated energy by large bending of an organic single crystal undergoing twinning deformation†

Sajjad Husain Mir,^a Yuichi Takasaki,^{ab} Emile R. Engel^a
and Satoshi Takamizawa^{*a}

We demonstrate exceptional twinning deformation in a molecular crystal upon application of mechanical stress. Crystal integrity is preserved and the deformation is associated with a large bending angle (65.44°). This is a new strategy to increase the magnitude of the dissipated energy in an organic solid comparable to that seen in alloys. By X-ray crystallographic analysis it was determined that a large molecular rearrangement at the twinning interface preserves the crystal integrity. Drastic molecular rearrangement at the twinning interface helps to preserve hydrogen bonding in the molecular rotation, which facilitates the large bending angle. The maximum shear strain of 218.81% and dissipated energy density of 1 MJ m⁻³ can significantly enhance mechanical damping of vibrations.

Received 21st March 2018
Accepted 9th June 2018

DOI: 10.1039/c8ra02499e

rsc.li/rsc-advances

Introduction

Twinning deformation is a type of plastic deformation that has been extensively investigated in metal alloys, mostly from the perspective of physics and materials science.¹ There are only a few examples of twinning deformation reported for organic crystals. This could be due to the typical fragility and tiny size of organic crystals. The dissipated energy (E_d) derived from twinning deformation of alloys and organic single crystals depends on the following factors: (i) coercive stress (σ_c) and (ii) bending angle (θ), given as ($E_d = \sigma_c \tan \theta$). In alloys the required magnitude of σ_c is larger than in the case of molecular crystals, deriving a significant magnitude of E_d . However, the value of θ is usually smaller in alloys than in organic crystals. The E_d value in alloys (usually 10^3 to 10^4 kJ m⁻³) is much higher than in typical organic solids (approximately 10^2 kJ m⁻³). Application of a relatively smaller σ_c in the deformation of organic single crystals can produce a large θ without crystal cleavage. Achievement of a large θ paves the way for new design principles to increase the value of E_d in organic single crystals. Moreover, alloys have polycrystalline properties so on average θ is reduced due to their isotropic nature, whereas, in organic single crystals the composition is almost anisotropic and associated with

comparatively higher values of θ which is advantageous for achieving enhancing E_d .

Some of the reports of twinning deformation in single crystals relate to organometallic compounds such as ferrocene² and tetramethyle-tetraselenafulvalene (TMTSF)₂X³ (X = ClO₄, PF₆, AsF₆, and NO₃), while among organic solids the following examples have been reported: 1,3,5-tribromo-2,4,6-triiodobenzene,⁴ 1,3,5-trichloro-2,4,6-triiodobenzene,⁴ L-lysine monohydrochloride dihydrate,⁵ and adipic acid doped with 3-methyl adipic acid.⁶ Studies of twinning deformation in such organic or organometallic solids are underdeveloped in contrast to the studies in metallic solids⁷ involving a control of their mechanical durability or deformability.

Recently, our research group has reported some stress-induced twinning deformation in organic single crystals,^{8–11} supported with experimental evidence by microscopic observations, X-ray crystal structure analysis, and force measurements. For example, the organosuperelastic crystals of the planar molecule 3,5-difluorobenzoic acid⁸ showed exceptional twinning. Crystal of 5-chloro-2-nitroaniline⁹ exhibited twinning ferroelasticity. The flexible rod shaped adipic acid molecule showed ferroelasticity driven by conformational change.¹⁰ Finally, a non-planar 4,4'-dicarboxydiphenyl ether¹¹ exhibited ferroelasticity by partial ring flipping. However, the bending angles in these crystals were 27.8°, 49.21°, 44.65°, and 16.9°, respectively. Moreover, the E_d value of these crystals is not so high as compared to that of alloys. Herein, we investigated twinning deformation in a single crystal of 2-methyl-5-nitrobenzoic acid (C₇H₈NO₄). Our results indicate exceptional mechanical twinning with an unprecedentedly large bending angle and large coercive stress, which requires drastic molecular rearrangement at the twinning interface to preserve the

^aDepartment of Materials System Science, Graduate School of Nanobioscience, Yokohama City University, 22-2 Seto, Kanazawa-ku, Yokohama, Kanagawa, 236-0027, Japan. E-mail: staka@yokohama-cu.ac.jp

^bKanagawa Institute of Industrial Science and Technology, Shimo-Ogino, 705-1 Ebina, Kanagawa, 243-0435, Japan

† Electronic supplementary information (ESI) available. CCDC 1831132 and 1831133. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c8ra02499e


hydrogen bonding and avoid crystal cleavage. These factors contribute towards a large E_d , which is an important property for mechanical damping of vibrations.

Results and discussion

2-Methyl-5-nitrobenzoic acid ($C_7H_8NO_4$) (**1**) (Scheme 1) is a beige colored aromatic compound with a high melting point of 184 °C. **1** is an important simple compound serving as a raw material for pharmaceuticals, agrochemicals, and dyes. Well-shaped, pale yellow colored rods with typical lengths of 0.2–1.0 mm and thicknesses of 0.1–0.3 mm were obtained by recrystallization of **1** from acetone at 298 K.

Twinning deformation was induced in a single crystal by the application of compression stress perpendicular to $(110)_{\alpha_0}$ and $(\bar{1}\bar{1}0)_{\alpha_0}$ (mother domain: α_0) crystal faces at 298 K. The crystal deformed in a diffusionless manner (Fig. 1a). The bending angle is estimated to be 65.44° between α_0 and α_1 (α_1 : twinned domain), which corresponds to the angle between $(0\bar{3}1)_{\alpha_0}$ and $(03\bar{1})_{\alpha_1}$, which agrees well with the value 64.28° obtained by measurement from the optical microscope (Fig. 1a). It is surprising that such a large bending can be achieved without considerably damaging the crystal.

Single-crystal X-ray structure analysis confirmed the twinning deformation under shear force. Both the α_0 and α_1 crystal structures have an identical crystal structure with the same symmetry *i.e.* triclinic crystal system and $P\bar{1}$ space group¹² (Table S1†). According to the indices of crystal faces in the bent shape as shown in Fig. 1b, the twinning interface is $(\bar{2}1\bar{1})_{\alpha_0}/(2\bar{1}1)_{\alpha_1}$. The α_1 domain is related to α_0 domain by a 180° rotation about the axis along $[013]_{\alpha_0}$ (Fig. 1b). The deformation requires drastic molecular rearrangement when the interface passes through the molecule. Considering the lattice correspondence require to achieve the bent crystal shape, the continuity of hydrogen bonding across the interface connecting α_0 and α_1 domains should be ensured by adjustment of the molecular orientations facing at the interface and the strength of hydrogen bonding between molecules at the interface. Molecules at the twinning interface are surrounded by four other neighboring molecules, that keeps hydrogen bonding stronger on passing of rotational plane. We presume this facilitates large bending without crystal cleavage. A similar speculation was indicated in the elastic curvature of an organic single crystal.¹³ Typical O–H...O hydrogen bonding between carboxylic acid groups occurs along $[013]$ with the C–O distance of 2.639 Å (intermolecular dotted lines in Fig. 2b). In addition, there are C–H...O interactions along $[0\bar{3}1]$ between the aromatic hydrogen H and O on the nitro group with C–O distance of 2.673 Å. The combination of O–H...O and C–H...O hydrogen bonds

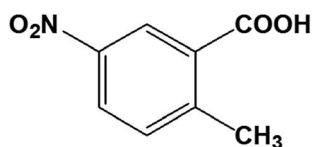

Scheme 1 Molecular structure of 2-methyl-5-nitrobenzoic acid (**1**).

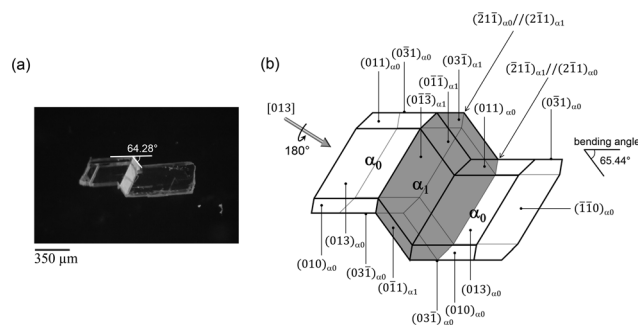


Fig. 1 (a) Optical image of the twinned crystal, prepared by compression on crystal surface $(110)_{\alpha_0}$, $[013]$ and (b) crystal face indices of the mechanically twinned crystal.

constitutes 2D arrangement in the plane of $(013)_{\alpha_0}$. The hydrogen bonding between carboxylic acid groups is the dominant force over weak van der Waals interactions between nitro and aromatic hydrogen atoms.

The maximum strain of **1** is expected to be 218.81% from $\tan\theta$, where θ is the bending angle. This calculated maximum strain is higher than for previous reports on organic crystals that have comparatively smaller bending angles than **1**. For example, the strain values for $(TMTSF)_2ClO_4$,^{14a} $(TMTSF)_2PF_6$,^{14c} 3,5 difluorobenzoic acid,⁸ and 5-chloro-2-nitroaniline⁹ are 33.3%, 36%, 52.7% and 115.9%, respectively. Moreover, the strain value is higher than for certain twinned metals. For examples, the values for gold nanopillars^{15a} and copper nanowires^{15b} are 5% and 7.2%, respectively.

We also conducted compression measurements of a single-crystal specimen. Despite the large bending angle and the brittleness of the crystal we could successfully induce twinning by loading stress along the long axis of the crystal (Fig. 3a). We prevented crystal breakage by avoiding stress perpendicular to the crystal surface. Because we presume if stress is perpendicular to the surface, components of the stress are in opposite

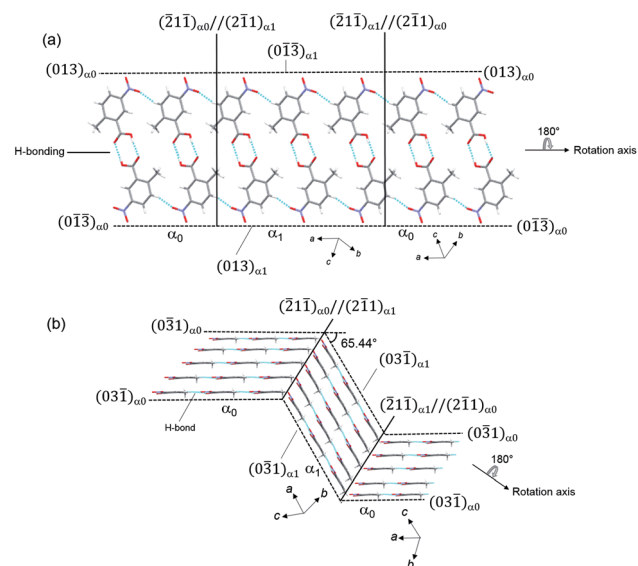


Fig. 2 Crystal packing diagram projected along (a) $(013)_{\alpha_0}$ and (b) $(031)_{\alpha_0}$.



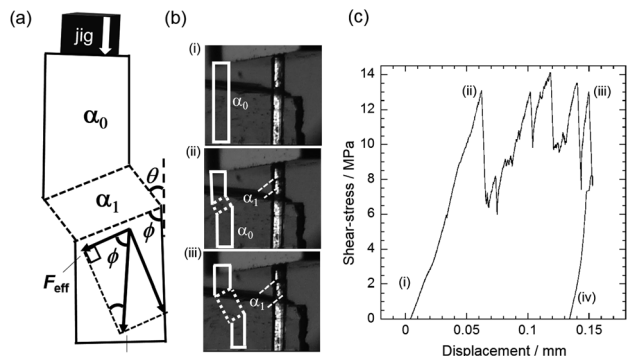


Fig. 3 Measurement of stress–strain curve, (a) cartoon illustration of crystal deformation pattern and force components, (b) snapshots of the twinning deformation of shear-stress (i–iii) (Movie S1†) with inset sketches of the deformation pattern, and (c) stress–strain curve at 298 K.

direction at the interface, that causes separation of the crystal at the twinning interface. Whereas, compression causes effective stress components in the direction as shown in Fig. 3a that prevents crystal breakage at the interface on twinning deformation. Therefore, a stress–strain curve was obtained by compressing the crystal *via* the crystal surface $(110)_{\alpha_0}$ (Fig. 3a), which derives the effective force along the angle 57.28° between twinning interface and effective shear. The effective stress that causes twinning deformation was derived by applying the formula (F_{eff} /cross-sectional area of the α_0/α_1 boundary), *i.e.* $(13.40 \times 10^{-15} \text{ m}^2)$ (Fig. 3a). One end of a single-crystal was fixed to a glass stage with a glue. A glass jig was then pushed against the $(110)_{\alpha_0}$ crystal surface at a constant speed of $30 \mu\text{m min}^{-1}$ (ESI, Movie S1†). As shown in Fig. 3c, stress was detected after the glass jig reached the crystal surface and an increase in the loading force began (3c(i and ii)). The effective stress reached 6.891 MPa at which point the twinning interface was generated (3c(ii)). The coercive stress achieved is the largest amongst all reports.^{8–11} The α_1 domain started to grow from both sides of the crystal. The growth of the α_1 domain was not smooth, producing spikes (3c(ii and iii)) in the curve. This could be ascribed to the generation of the multiple domains. On holding the displacement of the jig, the α_1 remained present and strain was recorded by removing the stress (iii and iv). The estimated dissipated strain energy was calculated as 1000 kJ m^{-3} ($0.6796 \text{ kJ kg}^{-1}$, and $123.109 \text{ J mol}^{-1}$). Based on the equation ($E_d = \sigma_c \tan \theta$), the E_d value of **1** is 65.24 times larger than the corresponding value for 3,5-difluorobenzoic acid *i.e.* 15.47 kJ m^{-3} (0.010 kJ kg^{-1} , 1.642 J mol^{-1}),⁸ and 4.67 times larger than in the case of 5-chloro-2-nitroaniline *i.e.* 216 kJ m^{-3} (0.136 kJ kg^{-1} , 23.46 J mol^{-1}).⁹ This large value of E_d is comparable to that of alloys and much higher than typical for organic solids. Since E_d is a derivative of the applied shear stress (σ) and deformation angle (θ) of the crystal, such dissipated energy density is expected to be increased by enlarging the bending angle of the crystal, which in this case is 64.28° (Fig. 1a), and/or the required shear stress for the deformation. The high dissipated energy will be effective for the damping of mechanical vibrations.

Conclusions

We confirmed a new strategy to increase E_d in organic single crystal, which typically bears smaller stress than those of metallic solids. Large bending angle in twinning ferroelastic deformation enables a wider crystal deformation range for the realization of large energy dissipation. The relationship between effective bending angle and E_d can be clearly measured in single crystals without breakage by microscopic and macroscopic experiments. The maximum strain and the E_d value in **1** is, to the best of our knowledge, the largest reported molecular crystals, facilitated by large deformation but with a smaller shear force. Such controllability paves the way for new design principles to increase the value of E_d in organic single crystals. The combination of small σ_c and large E_d makes organic ferroelastic materials promising for applications in mechanical damping, with high susceptibility to absorb weak shocks effectively by their small volume.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by SUZUKI, KISTEC, 2016–2018 Strategic Research Promotion (SK2810) fund of Yokohama City University for S. T., and the JSPS KAKENHI grants 17H06368 (grant-in-aid for Scientific Research on Innovative Areas), 17K19143 (grant-in-aid for Challenging Research (Pioneering)) for S. T. and 16H0710 (grant-in-aid for Research Activity start-up) for Y. T.

Notes and references

- 1 D. Zhang, L. Jiang, B. Zheng, J. M. Schoenung, S. Mahajan, E. J. Lavernia and I. J. Beyerlein, *Deformation Twinning (Update), Reference Module in Materials Science and Materials Engineering*, 2016, DOI: 10.1016/B978-0-12-803581-8.02878-2.
- 2 Y. Miyamoto and S. Takamizawa, *Dalton Trans.*, 2015, **44**, 5688–5691.
- 3 H. Schwenk, K. Neumair, K. Andres, F. Wudl and E. Aharon-Shalom, *Mol. Cryst. Liq. Cryst.*, 1982, **79**, 277.
- 4 C. M. Reddy, M. T. Kirchner, R. C. Gundakaram, K. A. Padmanabhan and G. R. Desiraju, *Chem.–Eur. J.*, 2006, **12**, 2222.
- 5 R. Bandyopadhyay and D. J. W. Grant, *Pharm. Res.*, 2002, **19**, 491.
- 6 L. Williams-Seton, R. J. Davey, H. F. Lieberman and R. G. Pritchard, *J. Pharm. Sci.*, 2000, **89**, 346.
- 7 I. Yoshida, D. Monma, K. Lino, K. Otsuka, M. Asai and H. Tsuzuki, *J. Alloys Compd.*, 2003, **355**, 79–84.
- 8 S. Takamizawa and Y. Takasaki, *Angew. Chem., Int. Ed.*, 2015, **54**, 4815–4817.
- 9 S. H. Mir, Y. Takasaki, E. R. Engel and S. Takamizawa, *Angew. Chem., Int. Ed.*, 2017, **56**, 15882–15885.



- 10 S. H. Mir, Y. Takasaki and S. Takamizawa, *Phys. Chem. Chem. Phys.*, 2018, **20**, 4631.
- 11 E. R. Engel, Y. Takasaki, S. H. Mir and S. Takamizawa, *R. Soc. Open Sci.*, 2018, **5**, 171146.
- 12 Crystal data of **1** for the α_0 phase (mother phase) at 298 K (CCDC-1831132): triclinic, $P\bar{1}$, $a = 7.611$ (15) Å, $b = 10.47$ (2) Å, $c = 10.55$ (2) Å, $\alpha = 89.45$ (3)°, $\beta = 81.45$ (3)°, $\gamma = 76.75$ (3)°, $V = 810$ (3) Å³, $Z = 4$, $D_{\text{calc.}} = 1.485$ Mg m⁻³, $R_1 = 0.0601$, $wR_2 = 0.1786$ for 1243 reflections with $I > 2\sigma(I)$ (for 1674 reflections (2759 total measured)), goodness-of-fit on $F_2 = 1.071$, largest diff. peak (hole) = 0.233 (−0.243) e Å⁻³. The α_1 phase (twinned phase) at 298 K (CCDC-1831133): triclinic, $P\bar{1}$, $a = 7.636$ (13) Å, $b = 10.426$ (19) Å, $c = 10.520$ (18) Å, $\alpha = 89.28$ (3)°, $\beta = 81.80$ (3)°, $\gamma = 76.32$ (3)°, $V = 805$ (2) Å³, $Z = 4$, $D_{\text{calc.}} = 1.494$ Mg m⁻³, $R_1 = 0.1016$, $wR_2 = 0.3546$ for 1500 reflections with $I > 2\sigma(I)$ (for 1554 reflections (2769 total measured)), goodness-of-fit on $F_2 = 1.161$, largest diff. peak (hole) = 0.466 (−0.431) e Å⁻³. CCDC-1831132, 1831133 contain the supplementary crystallographic data for this paper.
- 13 A. K. Saini, K. Natarajan and S. M. Mobin, *Chem. Commun.*, 2017, **53**, 9870.
- 14 (a) H. Schwenk, K. Andres, F. Wudl and E. Aharon-Shalom, *J. Phys.*, 1983, **44**, 1041–1045; (b) K. Kawabata, Y. Hosokawa, T. Kawauchi and T. Sambongi, *Ferroelectrics*, 2001, **251**, 199–205; (c) K. Kawabata, T. Saga, K. Matsuda, K. Nenoto and T. Sambongi, *Europhys. Lett.*, 2003, **64**, 118–123.
- 15 (a) K. A. Afanasyev and F. Sansoz, *Nano Lett.*, 2007, **7**, 2056; (b) Y. Yue, P. Liu, Z. Zhang, X. Han and E. Ma, *Nano Lett.*, 2011, **11**, 3151.

