


ChemComm

Accepted Manuscript

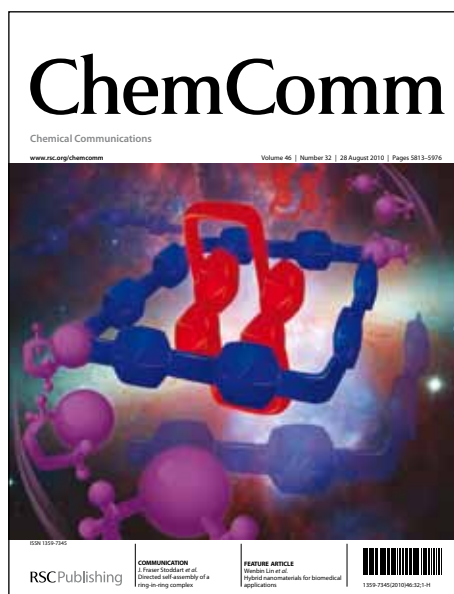

This is an *Accepted Manuscript*, which has been through the RSC Publishing peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, which is prior to technical editing, formatting and proof reading. This free service from RSC Publishing allows authors to make their results available to the community, in citable form, before publication of the edited article. This *Accepted Manuscript* will be replaced by the edited and formatted *Advance Article* as soon as this is available.

To cite this manuscript please use its permanent Digital Object Identifier (DOI®), which is identical for all formats of publication.

More information about *Accepted Manuscripts* can be found in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics contained in the manuscript submitted by the author(s) which may alter content, and that the standard [Terms & Conditions](#) and the [ethical guidelines](#) that apply to the journal are still applicable. In no event shall the RSC be held responsible for any errors or omissions in these *Accepted Manuscript* manuscripts or any consequences arising from the use of any information contained in them.

Negative area compressibility in silver(I) tricyanomethanide[†]

Sarah A. Hodgson,^a Jasper Adamson,^a Sarah J. Hunt,^a Matthew J. Cliffe,^a Andrew B. Cairns,^a Amber L. Thompson,^a Matthew G. Tucker,^{b,c} Nicholas P. Funnell,^a and Andrew L. Goodwin^{a,*}

Received Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

First published on the web Xth XXXXXXXXXX 200X

DOI: 10.1039/b000000x

The molecular framework $\text{Ag}(\text{tcm})$ ($\text{tcm}^- = \text{tri-cyanomethanide}$) expands continuously in two orthogonal directions under hydrostatic compression. The first of its kind, this negative area compressibility behaviour arises from the flattening of honeycomb-like layers during rapid pressure-driven collapse of the interlayer separation.

In the absence of a structural phase transition, it is a thermodynamic requirement that a system reduce its volume under hydrostatic pressure.¹ The phenomenon of negative compressibility is the counterintuitive effect whereby this volume reduction couples to an expansion of the material in at least one linear dimension.² Examples of such behaviour are rare even amongst anisotropic materials because buckling and bond compression mechanisms are almost always more effective at reducing crystal volume than is uniaxial or biaxial lattice expansion. Not only does the existence of negative compressibility challenge our understanding of the ways in which materials can respond to external stimuli, but the phenomenon is also of practical importance. It promises a means of developing artificial muscles, nanoscale actuators and high-performance pressure sensors for sonar and altitude measurements.^{2,3} In principle, the most extreme such response allowed thermodynamically is that of negative area compressibility (NAC), whereby a material expands along two orthogonal directions on increasing pressure. The possibility that tetragonal PbTiO_3 might show an extremely weak NAC effect has been raised⁴ and disputed;⁵ similarly weak effects are thought to occur at high pressure in NaV_2O_5 (Ref. 6) and are predicted for TlGaSe_2 .⁷ Instead the remarkably few negative compressibility materials that have been characterised unambiguously expand along only one principal axis when compressed hydrostatically (*i.e.*, negative linear compressibility,

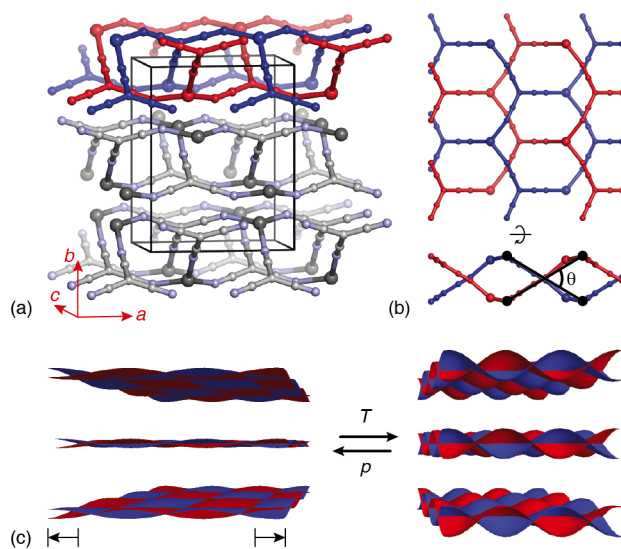


Fig. 1 (a) The crystal structure of $\text{Ag}(\text{tcm})$ is composed of stacked, doubly-interpenetrating (6,3)-nets in which both Ag^+ (large spheres) and tcm^- ions (smaller spheres) function as trigonal nodes. (b) The extent of rippling of layers (viewed along b and a in the top and bottom parts of this panel, respectively) can be quantified by the inter-network angle θ (see SI). (c) The generic mechanical response of a layered material links volume expansion to increasing interlayer separation and increasing layer rippling. The cross-sectional area of each layer is maximised by reducing θ , and hence increases during volume reduction under hydrostatic compression.

NLC).^{8–12} The distinction between NLC and NAC is more fundamental than magnitude alone: NAC materials increase their surface area under hydrostatic pressure, and so they can be used as substrates to provide order-of-magnitude amplification of piezoelectric response in *e.g.* ferroelectric sensors.²

One strategy for identifying negative compressibility candidates is to target framework materials that exhibit anisotropic negative thermal expansion (NTE): a material that shrinks in one direction on heating is likely to expand in that same direction on compression.¹³ While there is no requirement that deformation mechanisms under temperature and pressure be identical,¹⁴ there is empirical evidence of such a corre-

[†] Electronic Supplementary Information (ESI) available: Synthesis; experimental methods; X-ray single-crystal diffraction refinement details (variable-temperature and variable-pressure); neutron powder diffraction refinement details; calculations.

^a Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford OX1 3QR, U.K. Fax: +44 1865 274690; Tel: +44 1865 272137; E-mail: andrew.goodwin@chem.ox.ac.uk. ^b ISIS Facility, Rutherford Appleton Laboratory, Chilton, Didcot, OX11 0QX, U.K. ^c Diamond Light Source, Harwell Campus, Didcot, OX11 0DE, U.K.

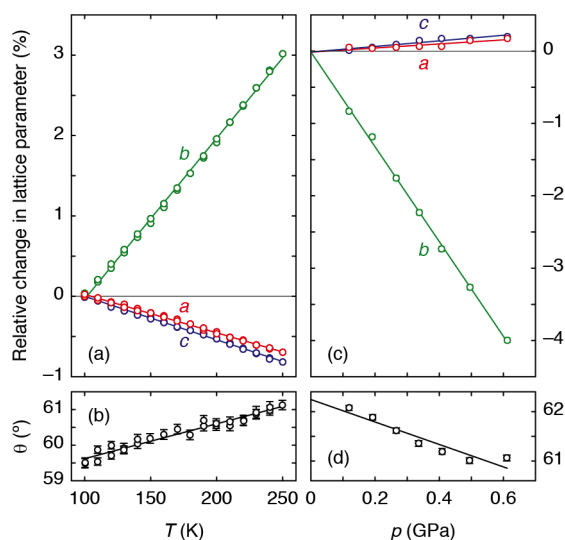


Fig. 2 (a) The thermal variation of lattice parameters, determined using single-crystal X-ray diffraction measurements, is illustrated here for ease of comparison as a % change relative to the extrapolated value at 100 K. Solid lines are weighted linear fits to the data obtained using the program PASCAL.¹⁷ (b) The corresponding variation in inter-network angle θ indicates an increase in layer rippling on heating. (c) The pressure dependence of lattice parameters, measured using variable-pressure neutron diffraction, is represented as a % change relative to the extrapolated value at 0 GPa. (d) The corresponding variation in θ now indicates a decrease in layer rippling under compression.

spondence amongst molecular framework materials.^{8,11,12,15} The natural strategy then for identifying NAC candidates is to investigate framework materials that exhibit area-NTE. It is for this reason that we chose to investigate silver(I) tricyanomethanide, $\text{Ag}(tcm)$: its layer-like network topology [Fig. 1(a)] is of a form often associated with area-NTE.^{16,17} In this compound, each Ag^+ cation is coordinated by three tcm^- anions in an approximately trigonal arrangement; likewise each tcm^- anion is coordinated by three Ag^+ centres.^{18,19} The resulting hexagonal (6,3) topology is sufficiently open that two honeycomb networks interpenetrate within each layer of the crystal structure [Fig. 1(b)]. Adjacent layers interact *via* long $\text{Ag}\cdots\text{N}$ contacts [$d(\text{Ag}\cdots\text{N}) > 3 \text{ \AA}$] that are sufficiently weak that the material behaves essentially as a two-dimensional framework, capable even of intercalation chemistry.¹⁹

Using single-crystal X-ray diffraction, we first established the thermal expansion behaviour of $\text{Ag}(tcm)$ to verify whether or not the material exhibits area-NTE. Because the material crystallises in the orthorhombic (polar) space group $Ima2$,¹⁸ its thermal expansivity is uniquely determined by the relative rate of change of the unit cell lengths with temperature.¹⁷ We observe essentially linear thermal variation in these parameters over the temperature range 100–250 K [Fig. 2(a)], yield-

ing coefficients of thermal expansion of $-48(3)$, $+200(2)$ and $-54.0(4) \text{ MK}^{-1}$ along the a , b , and c axes, respectively.¹⁷ As is increasingly found to be the case for molecular frameworks,^{13,20} the magnitudes of these values are large indeed compared to those obtained for traditional engineering materials, for which one expects linear coefficients of thermal expansion in the vicinity of $+20 \text{ MK}^{-1}$ (*i.e.*, a 0.2% increase in linear dimension for each 100 K temperature rise).²¹ What is clear is that $\text{Ag}(tcm)$ does indeed exhibit area-NTE, with an area coefficient of thermal expansion for the (a,c) -plane, $\alpha_{(010)} = -102(3) \text{ MK}^{-1}$, that is the most extreme negative value reported for a layered material. The material undergoes a 1% reduction in area for each 100 K rise in temperature—more than an order of magnitude larger than the corresponding values for area-NTE systems such as graphite and $\text{Ni}(\text{CN})_2$ ($\alpha_A = -2.4$ and -13 MK^{-1} , respectively).^{17,22,23}

The microscopic mechanism responsible for this behaviour can be deduced from the variation in framework geometry during heating. The established model of area-NTE in layered materials predicts coupling between NTE and the extent of layer ‘rippling’, as quantified by the inter-network torsion angle θ [Fig. 1(b,c)].¹⁶ Our measurements indeed indicate an increase in θ with temperature [Fig. 2(b)].²⁴ Using simple geometric arguments, the temperature dependence of θ can be used to estimate the value of α_A attributable to layer rippling:

$$\alpha_A^{\text{calc}} = -\theta \tan\left(\frac{\theta}{2}\right) \alpha_\theta, \quad (1)$$

where $\alpha_\theta = d(\ln \theta)/dT$ (see SI for derivation). Our data give $\alpha_A^{\text{calc}} = -101 \text{ MK}^{-1}$, which is within experimental error of the observed value of $-102(3) \text{ MK}^{-1}$. Consequently, we can be confident that the mechanism illustrated in Fig. 1(c) is responsible for area-NTE in $\text{Ag}(tcm)$.

In order to determine whether or not $\text{Ag}(tcm)$ exhibits the target property of NAC, we performed a series of neutron diffraction measurements across the pressure range $0 < p < 2 \text{ GPa}$ using the PEARL instrument at ISIS. The use of neutron radiation helps maximise the scattering contrast between Ag and C/N atoms, which is all the more important for measurements performed in the high-background sample environments required for variable-pressure experiments. We found that, for powdered samples, the ambient phase is stable up to $0.615(6) \text{ GPa}$, but by $0.672(7) \text{ GPa}$ it has transformed reversibly to a related phase with symmetry not higher than monoclinic. The same transformation occurs at higher pressures ($0.83 < p_c < 1.47 \text{ GPa}$) in single-crystal experiments (see SI for further discussion); our focus here is on the pressure-dependent behaviour of the ambient phase rather than the nature of the phase transition or the high-pressure phase. Rietveld refinement against the corresponding neutron diffraction patterns revealed the anticipated increase in a and c parameters is evident from these data [Fig. 2(c)], with the

anomalous expansion of the material in these directions being allowed by a much more rapid decrease in the interlayer spacing (given by the lattice parameter b). Our variable-pressure lattice parameter data can be converted into compressibilities using the relationship $K_\ell = -[\partial(\ln \ell)/\partial p]_T$, from which we obtain $K_a = -3.5(6) \text{ TPa}^{-1}$, $K_b = +66(20) \text{ TPa}^{-1}$, and $K_c = -4.0(6) \text{ TPa}^{-1}$. Consequently, the compressibility is negative everywhere within the (a, c) -plane, with the magnitude of NAC quantified by the corresponding area compressibility $K_{(010)} = K_a + K_c = -7.5(8) \text{ TPa}^{-1}$.

Conventional engineering materials (*e.g.* iron) have linear compressibilities $K \sim 5 \text{ TPa}^{-1}$ that correspond to a decrease of *ca* 0.5% in length for each 1 GPa pressure increase;²⁵ consequently, the NAC behaviour of Ag(*tcm*) is essentially as strong as the positive area compressibility of these ‘normal’ phases. Moreover, despite the fact that the orthorhombic symmetry of Ag(*tcm*) allows for different behaviour in the **a** and **c** directions, we find that both its compressibility and its thermal expansivity are essentially isotropic within the entire (a, c) plane. Isotropy is important for NAC applications because it avoids composite warping and performance breakdown.²

That NAC is driven by the same layer-rippling mechanism as area-NTE is evident in the variation of the parameter θ with increasing pressure [Fig. 2(d)]. The volume reduction accommodated by rapid collapse of the interlayer spacing (note $K_b \gg 5 \text{ TPa}^{-1}$) evidently couples with a reduction in the degree of layer rippling: $d\theta/dp < 0$. To substantiate further our interpretation of the NAC mechanism, we recast Eq. (1) in terms of compressibilities; our refined values of θ give $K_A^{\text{calc}} = -\theta \tan(\theta/2) K_\theta = -26 \text{ TPa}^{-1}$. That the measured area compressibility $K_{(010)} = -7.5(8) \text{ TPa}^{-1}$ is somewhat smaller in magnitude reflects the expected $\sim 10 \text{ TPa}^{-1}$ contribution from (positive) bond compressibilities omitted from the geometric formalism of Eq. (1), as discussed elsewhere for NLC materials.¹³ Indeed, that the p/T correspondence inferred in Fig. 1(c) holds qualitatively for Ag(*tcm*) is immediately evident in the close relationship between the temperature- and pressure-induced lattice parameter and layer rippling parameter variations documented in Fig. 2.

In conclusion, we find that silver(I) tricyanomethanide exhibits NAC over the pressure range $0 < p < 0.612 \text{ GPa}$ with an essentially isotropic area compressibility of similar magnitude (but opposite sign) to that of established engineering materials. From a structural viewpoint, the phenomenon can be understood in terms of pressure-driven damping of layer ‘rippling’, acting to increase the layer cross-sectional area at larger hydrostatic pressures. Variable-pressure spectroscopic measurements may provide valuable additional insight into the subtle variations in bonding interactions that occur throughout this process.²⁶ In favour of immediate application of Ag(*tcm*) in ultra-high-precision sensing devices are (i) the ease with which large single crystal samples can be prepared under am-

bient conditions and using readily-available solvents, and (ii) its optical transparency. Moreover, the polarity of its crystal structure offers the possibility of designing multifunctional devices based on Ag(*tcm*) in which the interplay between responses to electric field, temperature, and pressure are exploited to produce piezoelectric and thermoelectric devices.

The authors gratefully acknowledge financial support from the E.P.S.R.C. (EP/G004528/2) and the E.R.C. (Grant Ref.: 279705), the provision of neutron beamtime on the PEARL instrument at ISIS, and the assistance of Dr Marek Jura (ISIS).

References

- 1 Z. G. Nicolaou and A. E. Motter, *Nature Mater.*, 2012, **11**, 608–613.
- 2 R. H. Baughman, S. Stafström, C. Cui and S. O. Dantas, *Science*, 1998, **279**, 1522–1524.
- 3 A. E. Aliev, J. Oh, M. E. Kozlov, A. A. Kuznetsov, S. Fang, A. F. Fonseca, R. Ovalle, M. D. Lima, M. H. Haque, Y. N. Gartstein, M. Zhang, A. A. Zakhidov and R. H. Baughman, *Science*, 2009, **323**, 1575–1578.
- 4 R. J. Nelmes and A. Katrusiak, *J. Phys. C: Solid State Phys.*, 1986, **19**, L725–L730.
- 5 A. Sani, M. Hanfland and D. Levy, *J. Phys.: Cond. Matt.*, 2002, **14**, 10601–10604.
- 6 I. Loa, K. Syassen, R. K. Kremer, U. Schwarz and M. Hanfland, *Phys. Rev. B*, 1999, **60**, R6945–R6948.
- 7 M. Seyidov and R. A. Suleymanov, *J. Appl. Phys.*, 2010, **108**, 063540.
- 8 A. L. Goodwin, D. A. Keen and M. G. Tucker, *Proc. Natl. Acad. Sci., U.S.A.*, 2008, **105**, 18708–18713.
- 9 W. Li, M. R. Probert, M. Kosa, T. D. Bennett, A. Thirumurugan, R. P. Burwood, M. Parinello, J. A. K. Howard and A. K. Cheetham, *J. Am. Chem. Soc.*, 2012, **134**, 11940–11943.
- 10 H. J. Shepherd, T. Palamarciuc, P. Rosa, P. Guionneau, G. Molnár, J.-F. Létard and A. Bousseksou, *Angew. Chem. Int. Ed.*, 2012, **51**, 3910–3914.
- 11 A. B. Cairns, J. Catafesta, C. Levelut, J. Rouquette, A. van der Lee, L. Peters, A. L. Thompson, V. Dmitriev, J. Haines and A. L. Goodwin, *Nature Mater.*, 2013, **12**, 212–216.
- 12 A. D. Fortes, E. Suard and K. S. Knight, *Science*, 2011, **331**, 742–745.
- 13 J. M. Ogborn, I. E. Collings, S. A. Moggach, A. L. Thompson and A. L. Goodwin, *Chem. Sci.*, 2012, **3**, 3011–3017.
- 14 R. W. Munn, *J. Phys. C: Solid State Phys.*, 1972, **5**, 535–542.
- 15 A. B. Cairns, A. L. Thompson, M. G. Tucker, J. Haines and A. L. Goodwin, *J. Am. Chem. Soc.*, 2012, **134**, 4454–4456.
- 16 I. M. Lifshits, *Zh. Eks. Teor. Fiz.*, 1952, **22**, 475–486.
- 17 M. J. Cliffe and A. L. Goodwin, *J. Appl. Cryst.*, 2012, **45**, 1321–1329.
- 18 J. Konnert and D. Britton, *Inorg. Chem.*, 1966, **5**, 1193–1196.
- 19 S. R. Batten, B. F. Hoskins and R. Robson, *New J. Chem.*, 1998, 173–175.
- 20 A. L. Goodwin, M. Calleja, M. J. Conterio, M. T. Dove, J. S. O. Evans, D. A. Keen, L. Peters and M. G. Tucker, *Science*, 2008, **319**, 794–797.
- 21 R. E. Newnham, *Properties of Materials*, Oxford University Press, Oxford, 2005.
- 22 A. C. Bailey and B. Yates, *J. Appl. Phys.*, 1970, **41**, 5088–5091.
- 23 S. J. Hibble, A. M. Chippindale, A. H. Pohl and A. C. Hannon, *Angew. Chem. Int. Ed.*, 2007, **46**, 7116–7118.
- 24 P. Betteridge, J. Carruthers, R. Cooper, K. Prout and D. Watkin, *J. Appl. Cryst.*, 2003, **36**, 1487.
- 25 H. L. Zhang, S. Lu, M. P. J. Punkkinen, Q.-M. Hu, B. Johansson and L. Vitos, *Phys. Rev. B*, 2010, **82**, 132409.
- 26 K. Kamali, C. Ravi, T. R. Ravindran, R. M. Sarguna, T. N. Sairam and G. Kaur, *J. Phys. Chem. C*, 2013, **117**, 25704–25713.