

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Catalytic Activation of OKO Zeolite with Intersecting Pores of 10- and 12-Membered Rings using Atomic Layer Deposition of Aluminium

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

E. Verheyen^a, S. Pulinthanathu Sree^a, K. Thomas^b, J. Dendooven^c, M. De Prins^a, G. Vanbutsele^a, E. Breynaert^a, J.-P. Gilson^b, C.E.A. Kirschhock^a, C. Detavernier^c and J.A. Martens^a

Tetrahedral framework aluminium was introduced in all-silica zeolite -COK-14 using Atomic Layer Deposition (ALD) involving alternating exposure to trimethylaluminium and water vapour. The modification causes permanent conversion of the originally interrupted framework of -COK-14 to a fully connected OKO type framework, and generates catalytic activity in acid catalysed hydrocarbon conversion reaction.

Yearly, about 1 million tons of synthetic zeolites are produced in industry for catalytic applications.¹ While the Atlas of Zeolite Framework Types² counts over 200 framework types, only a limited number of topologies have been implemented in large scale industrial applications, viz. FAU, LTL, MOR, BEA, MWW, MFI, FER, AEL and TON.¹ These zeolites have a mono- or multidimensional channel system circumscribed by 12-membered rings of tetrahedra (12-MRs), or 10-MRs. While 10-MR zeolites are particularly attractive for their molecular shape selectivity, the 12-MR zeolites with their larger pores have a wider scope in acid catalysed reactions. Application limiting factors of candidate zeolites are instability and the lack of trivalent element substituted specimen with cation exchange capacity and Brønsted acidity. Zeolites which combine 10- and 12-MR pores are of particular interest, but their number is even more limited.³ The new interrupted all-silica -COK-14 zeolite and its fully connected form, COK-14, have such two-dimensional intersecting 10- and 12-MR pore system (Figure 1).⁴ This zeolite with OKO framework type has been obtained by inverse sigma transformation from the parent germanosilicate UTL zeolite⁵, and is probably isostructural to IPC-2, a zeolite made by the ADOR strategy (Assembly, Disassembly, Organization, Reassembly) departing from the same parent zeolite⁶. Degermanation of UTL zeolite to obtain -COK-14 is performed through acid leaching, which impedes aluminium incorporation in the framework because of its amphoteric behaviour.⁷ While direct introduction of aluminium

during synthesis often is problematic⁸, post-synthesis alumination of zeolites can offer a solution. Strategies such as a treatment with aqueous aluminate solution under hydrothermal conditions, or exposure to aluminium halide vapour have been reported in literature.⁹ Among the alternative options, Atomic Layer Deposition (ALD) is gaining importance in catalysis research.¹⁰ ALD is known as an elegant means of applying protective layers on metal nanoparticles, depositing platinum on the surface of graphene nanosheets, and for generating photocatalytic activity.^{10,11} Aluminium ALD (Al-ALD) has been demonstrated as a method to generate acid sites in nanoporous powders.¹¹ Alumination of ultrastable Y zeolite and hierarchical Zeolite-4 material by Al-ALD resulted in enhanced acid catalytic activity.¹¹ Previous attempt to activate 10-MR Silicalite-1 zeolite (MFI framework) using Al-ALD was not successful.¹¹ This is probably due to the pore size of Silicalite-1 being too narrow for adsorption of the trimethylaluminium (TMA) precursor molecule used in Al-ALD.¹¹ Here we report the successful introduction of tetrahedral aluminium in the all-silica -COK-14 zeolite by Al-ALD, and demonstrate the catalytic activation of OKO type zeolites for *n*-decane hydrocracking. This is a first example of generating acid sites in a purely siliceous zeolite by Al-ALD.

Interrupted framework -COK-14 zeolite was prepared by degermanation of UTL zeolite.⁴ Al-ALD was performed on -COK-14 in a high-vacuum ALD setup¹². Experimental details are provided in Supplementary Information. The Al-ALD treated sample was suspended in 0.5 M NH₄Cl solution and heated under reflux for 90 minutes, washed and dried to obtain the ammonium-exchanged form.

X-ray diffraction (XRD) revealed Al-ALD did not cause significant changes in structure and crystallinity, and showed the interrupted -COK-14 framework was preserved. Interrupted framework of all-silica -COK-14 can be transformed into fully connected OKO

framework of COK-14 zeolite by heating at temperatures of at least 300 °C.⁴ The transformation involves reorientation and condensation of silanol groups (Figure 1). All-silica OKO zeolite is stable only at elevated temperature in the absence of water.⁴ Upon hydration and cooling the structure transforms back to the interrupted framework.

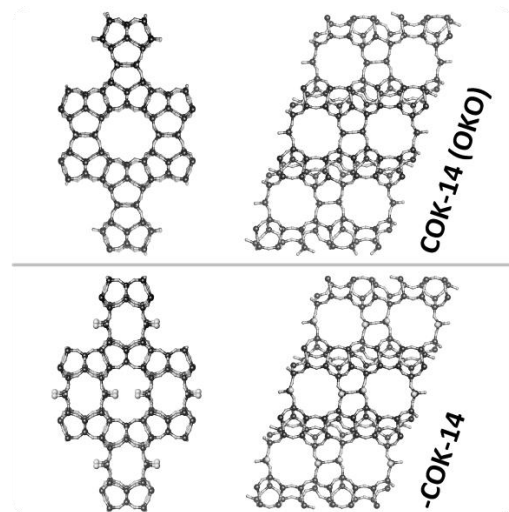


Figure 1 : Framework of COK-14 (OKO framework type) (top) and -COK-14 zeolite (bottom), viewed along the 12-MR pores (left) and 10-MR pores (right). Structural silanol groups in -COK-14 are protruding into the 12-MR channels.

For catalytic application, an ammonium-exchanged aluminosilicate zeolite needs to be pretreated at 400 °C to obtain the acid form. XRD revealed that ammonium-exchanged, Al-ALD treated -COK-14 zeolite after pretreatment at 400 °C was permanently transformed into fully connected COK-14 (Figure 2a). In contrast with the parent all-silica zeolite COK-14, it did not return to an interrupted framework upon hydration. The aluminosilicate COK-14 zeolite was stable upon storage for 3 months under ambient conditions without special precaution. ²⁷Al MAS NMR revealed a distribution of aluminium coordinations in Al-ALD treated, ammonium-exchanged COK-14 sample of ca. 21% tetrahedral Al, ca. 19% pentacoordinated or distorted tetrahedral Al, and 60% octahedral extra-framework Al (Figure 2b). According to EDX the Si/Al atomic ratio was around 50. Combining NMR and EDX data, the framework Si/Al atomic ratio was estimated at ca. 240. Remarkably, introduction of such very low amounts of aluminium via Al-ALD is sufficient to stabilise the fully connected OKO framework.

Framework transformation from aluminosilicate -COK-14 to COK-14 has a significant influence on the porosity. Nitrogen adsorption isotherms of aluminosilicate -COK-14 and aluminosilicate COK-14 indicated a pore size enlargement from 7.2 to 7.9 Å (SF method¹³). This widening is ascribed to the annealing of the framework and the elimination of silanol groups pointing into the 12-MR pores (Figure 1). Framework expansion by aluminium incorporation was considered to contribute less, given the small amount introduced.

COK-14 displays a platelet crystal morphology with plates of up to 10 μm and a typical thickness of around 100 nm. The intersecting 10- and 12-MR pores of COK-14 run parallel to the sheets⁴, such that the pore system is accessible only via the edges of the platelets.

The 10-MRs probably will be too narrow for adsorption of the TMA precursor of the Al-ALD process¹¹. TMA molecules are expected to penetrate via the 12-MR channels. The presence of Brønsted acid sites was revealed by FTIR spectroscopy after adsorption of pyridine (Figure 2c). Parent all-silica -COK-14 did not have any Brønsted acid sites retaining pyridine at 150 °C, as expected. In fully connected aluminosilicate COK-14 deammoniated and annealed at 400 °C, the total Brønsted acid site concentration was 6.5 mmol/kg (retaining pyridine at 150 °C), and the concentration of stronger acid sites retaining pyridine at 200 °C was 5 mmol/kg. This concentration of Brønsted acid sites probed with pyridine was about one tenth of the concentration of tetrahedral Al, which for a framework Si/Al ratio of 240 is estimated at ca. 70 mmol/kg. The presence of extra-framework aluminium species, detected with ²⁷Al MAS NMR (Figure 2b), neutralising framework charges can be responsible.

Ammonium-exchanged aluminosilicate -COK-14 was loaded with 0.5 wt.% Pt via incipient wetness impregnation with Pt(NH₃)₄Cl₂. Transformation to the fully connected OKO framework after pretreatment with oxygen followed by reduction in hydrogen at 400 °C was confirmed by XRD. A uniform distribution of Pt metal particles with sizes of around 6 nm was observed on the external surface of the zeolite crystals using NanoSEM (Figure 3).

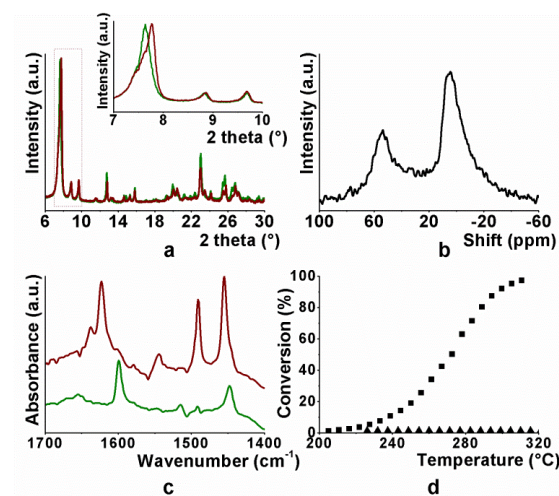


Figure 2 : (a) XRD of hydrated aluminosilicate -COK-14 before (green) and after thermal transformation to aluminosilicate COK-14 (red), (b) ²⁷Al MAS NMR spectrum of aluminosilicate COK-14, (c) FTIR spectra obtained after adsorption of pyridine on all-silica -COK-14 (green) and aluminosilicate COK-14 (red) after evacuation at 150 °C and (d) conversion of *n*-decane against reaction temperature on Pt-loaded all-silica COK-14 (▲) and Pt-loaded aluminosilicate COK-14 (■) (Reaction conditions : P_{H₂}/P_{C₁₀} = 214, W/F° = 980 kg s mol⁻¹, P = 0.45 MPa).

The catalytic activity of Pt-loaded all-silica and Pt-loaded aluminosilicate COK-14 was investigated in the hydroconversion of *n*-decane. The conversion of *n*-decane is plotted against reaction temperature in Figure 2d. Hydroisomerisation and hydrocracking of a long *n*-alkane are bifunctional catalytic processes in which the noble metal catalyses dehydrogenation and hydrogenation, while the carbon-carbon bonds of the *n*-alkane are rearranged on acid sites via alkylcarbenium ion chemistry.¹⁴ The parent purely siliceous COK-14 lacking Brønsted acid sites (Figure 2c) was inactive, as expected. Bifunctional Pt-loaded aluminosilicate COK-14 having Brønsted

acid sites was active and reached full conversion of *n*-decane at a reaction temperature of 310 °C. The robustness of this bifunctional OKO catalyst and the absence of deactivation were verified by running the recovered catalyst sample a second time 4 months later. The significant catalytic activity of this OKO zeolite with very low concentration of Brønsted acid sites (5 mmol/kg) is remarkable. The hydroisomerisation selectivity can be used to probe molecular shape selectivity.¹⁵ On 12-MR zeolites, the refined constraint index (CI°), representing the yield ratio of 2-methylnonane to 5-methylnonane at 5% conversion yield is in the range 1 - 2.5, while 10-MR zeolites favour 2-methylnonane formation and have higher CI°. The CI° value of COK-14 is 1.6, confirming the presence of 12-MR pores.

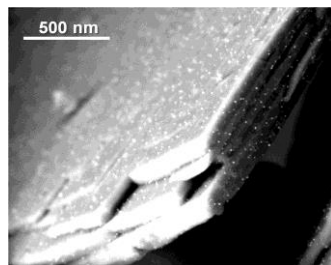


Figure 3 : NanoSEM image of Pt-loaded aluminosilicate COK-14 after catalysis. Pt particles appear as small white spots.

In conclusion, a stable aluminosilicate version of OKO zeolite was obtained by alumination of -COK-14 using Al-ALD, ammonium exchange and deammoniation at 400 °C. Introducing traces of Al through Al-ALD appeared sufficient to stabilise the fully connected OKO framework. Investigation of alternative heteroatom introduction methods to stabilise the fully connected OKO framework and deeper investigation of the origin of this stabilisation using multidimensional NMR and molecular modelling is ongoing. Al-ALD proved to be efficient for generating Brønsted acid sites in OKO zeolite. In this way, a stable aluminosilicate zeolite with 10- and 12-MR pores became available for acid catalysis. ALD originally has been developed for manufacturing of electronic compounds. Although application of ALD for massive catalyst production may be out of reach, it may be considered for preparation of model systems for scientific investigation, and perhaps for medium-scale production since efforts on automation and continuous processing currently are being made.¹⁶

Notes and references

^aCentre for Surface Chemistry and Catalysis, KU Leuven, Kasteelpark Arenberg 23, 3001 Leuven, Belgium.

^bLaboratoire Catalyse & Spectrochimie (LCS), ENSICAEN, 6 boulevard Maréchal Juin, 14050 Caen, France.

^cDepartment of Solid State Sciences, Ghent University, Krijgslaan 281–S1, 9000 Gent, Belgium.

J.A.M. acknowledges the Flemish government for long-term structural funding (Methusalem); C.D. the European Research Council (Starting Grant No. 239865) and the Special Research Fund BOF of Ghent University (GOA/01G01513); E.B. and J.D. FWO Vlaanderen for postdoctoral fellowships. K. Houthoofd is acknowledged for the NMR measurements.

† Electronic Supplementary Information available : Catalyst preparation, characterisation and *n*-decane hydroisomerisation and -cracking.

1 W. Vermeiren and J.-P. Gilson *Top. Catal.*, 2009, **52**, 1131.

- 2 <http://www.iza-structure.org/databases/>
- 3 R.F. Lobo, M. Pan, I. Chan, H.-X. Li, R.C. Medrud, S.I. Zones, P.A. Crozier and M.E. Davis, *Science*, 193, **262**, 1543; D.L. Dorset, S.C. Weston and S.S. Dhingra, *J. Phys. Chem. B*, 2006, **110**, 2045; R. Simancas, D. Dari, N. Velamazán, M.T. Navarro, A. Cantin, J.L. Jorda, G. Sastre, A. Corma and F. Rey, *Science*, 2010, **330**, 1219; T. Willhammar, J. Sun, W. Wan, P. Oleynikov, D. Zhang, X. Zou, M. Moliner, J. Gonzalez, C. Martínez, F. Rey and A. Corma, *Nat. Chem.*, 2012, **4**, 188.
- 4 E. Verheyen, L. Joos, K. Van Havenbergh, E. Breynaert, N. Kasian, E. Gobechiya, K. Houthoofd, C. Martineau, M. Hinterstein, F. Taulelle, V. Van Speybroeck, M. Waroquier, S. Bals, G. Van Tendeloo, C.E.A. Kirschhock, J.A. Martens, *Nat. Mater.*, 2012, **11**, 1059.
- 5 J.-L. Paillaud, B. Harbuzaru, J. Patarin, N. Bats, *Science*, 2004, **304**, 990; A. Corma, M.J. Díaz-Cabañas, F. Rey, S. Nicopoulus and K. Boulahya, *Chem. Commun.*, 2004, **12**, 1356.
- 6 W.J. Roth, O.V. Shvets, M. Shamzhy, P. Chlubná, M. Kubů, P. Nachtigall and J. Čejka, *J. Am. Chem. Soc.*, 2011, **133**, 6130; W.J. Roth, P. Nachtigall, R.E. Morris, P.S. Wheatley, V.R. Seymour, S.E. Ashbrook, P. Chlubná, L. Grajciar, M. Položij, A. Zukal, O. Shvets and J. Čejka, *Nat. Chem.*, 2013, **5**, 628.
- 7 N. Kasian, E. Verheyen, G. Vanbutsele, K. Houthoofd, T.I. Korányi, J.A. Martens and C.E.A. Kirschhock, *Micropor. Mesopor. Mat.*, 2013, **166**, 153.
- 8 C.-Y. Chen and S.I. Zones in *Zeolites and Catalysis: Synthesis, Reactions and Applications* ed. J. Čejka, A. Corma and S. Zones, Wiley-VHC, Weinheim, 2010, Vol. 1, pp. 155-167.
- 9 G.H. Kühn in *Catalysis and Zeolites, Fundamentals and Applications* ed J. Weitkamp and L. Puppe, Springer, 1999, pp. 81-198; M.W. Anderson, J. Klinowski and L. Xinsheng, *J. Chem. Soc., Chem. Commun.*, 1984, **23**, 1596; T. Yashima, K. Yamagishi, S. Namba, S. Nakata, S. Asaoka in *Innovation in zeolite materials science* ed P.J. Grobet, W.J. Mortier, E.F. Vansant and G. Schulz-Ekloff, Elsevier, 1988, pp. 175-182.
- 10 S.M. George, *Chem. Rev.*, 2010, **110**, 111; J. Lu, J.W. Elam and P.C. Stair *Acc. Chem. Res.*, 2013, **46**, 1806; S. Sun, G. Zhang, N. Gauquelin, N. Chen, J. Zhou, S. Yang, W. Chen, X. Meng, D. Geng, M.N. Bani, R. Li, S. Ye, S. Knights, G.A. Botton, T.-K. Sham and X. Sun, *Sci. Rep.*, 2013, **3**, 1.
- 11 S.P. Sree, J. Dendooven, T.I. Korányi, G. Vanbutsele, K. Houthoofd, D. Deduytsche, C. Detavernier and J.A. Martens, *Catal. Sci. Technol.*, 2011, **1**, 218; C. Detavernier, J. Dendooven, S.P. Sree, K.F. Ludwig and J.A. Martens, *Chem. Soc. Rev.*, 2011, **40**, 5242.
- 12 J. Musschoot, Q. Xie, D. Deduytsche, S. Van den Bergh, R.L. Van Meirhaeghe and C. Detavernier, *Microelectron. Eng.*, 2009, **86**, 72.
- 13 A. Saito and H.C. Foley, *AIChE J.*, 1991, **37**, 429.
- 14 J. Weitkamp, *ChemCatChem*, 2012, **4**, 292.
- 15 J.A. Martens, M. Tielen, P.A. Jacobs and J. Weitkamp, *Zeolites*, 1984, **4**, 98.
- 16 D. Longrie, D. Deduytsche and C. Detavernier, *J. Vac. Sci. Technol. A*, 2014, **32**, 010802-1; J.A. McCormick, B.L. Cloutier, A.W. Weimer and S.M. George, *J. Vac. Sci. Technol. A*, 2007, **25**, 67; P. Poodt, D.C. Cameron, E. Dickey, S.M. George, V. Kuznetsov, G.N. Parsons, F. Roozeboom, G. Sundaram and A. Vermeer, *J. Vac. Sci. Technol. A*, 2012, **30**, 010801-1.