

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Small Molecule BODIPY Dyes as non-Fullerene Acceptors in Bulk Heterojunction Organic Photovoltaics

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2014,
Accepted 00th January 2014


DOI: 10.1039/x0xx00000x

www.rsc.org/

A series of acceptor-donor-acceptor molecules containing terminal BODIPY moieties conjugated through the *meso* position were synthesized. Deep LUMO energy levels and good visible absorption led to their use as acceptors in bulk heterojunction solar cells. Inverted devices were fabricated, reaching efficiencies as high as 1.51%.

The field of organic photovoltaics (OPV) has advanced in recent years through extensive investigation into various conjugated polymer and small molecule structures. Most of these accomplishments have been focused on optimizing donors in bulk heterojunction (BHJ) organic solar cells, where the acceptor is primarily based on fullerenes.¹ While fullerene derivatives have several obviously attractive features for BHJ OPV devices,² the search for non-fullerene acceptors has gained significant attention in recent years, mainly driven by the possibility that the new acceptors could exhibit stronger absorption in the visible region of the electromagnetic spectrum.³ Concurrently, there also has been a surge in developing small molecules as active materials for OPVs, because of the reproducibility and the potential for frontier orbital energy level controls that they offer.^{1c,3c} The combination of these two interests has triggered the search for small molecule non-fullerene acceptors for BHJ OPV.^{1b,3b,4}

Considering that 4,4-difluoro-4-bora-3a,4a-diaza-s-indacene (BODIPY) based molecules exhibit a strong absorption in the visible region (>500 nm) and variable redox chemistry, we conceived the use of these molecules as acceptors in BHJ OPV devices.^{5, 6} Specifically, we hypothesized that acceptor-donor-acceptor (A-D-A) type molecules with BODIPY as the acceptor moiety will provide convenient access to

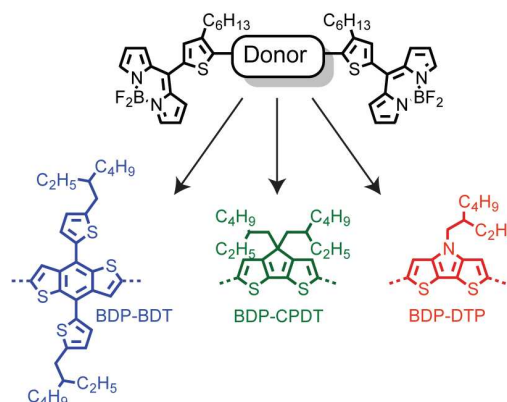

Scheme 1 Molecular structures of the BODIPY-based A-D-A molecules

low band-gap small molecules that could be tested as acceptors in BHJ devices. Herein, we report three such molecules, in which BODIPY is conjugated through its *meso* position using a 3-hexylthiophene linker to 4,8-bis(5-(2-ethylhexyl) thiophen-2-yl)benzo[1,2-*b*:4,5-*b'*]dithiophene, 4,4-bis(2-ethylhexyl)-4*H*-cyclopenta-[2,1-*b*:3,4-*b'*]dithiophene or *N*-(2-ethylhexyl)-dithieno [3,2-*b*:2',3'-*d'*]pyrrole to afford **BDP-BDT**, **BDP-CPDT**, and **BDP-DTP** respectively (Scheme 1). These molecules show strong visible absorption with low lying LUMO levels, making them electronically suitable as acceptors for many donor materials. To examine their potential as acceptors in BHJ OPVs, devices were fabricated using P3HT as the donor.

Syntheses of the molecules include the formation of a terminal unit composed of a BODIPY core substituted at the *meso* position with a brominated hexylthiophene, providing an additional solubilizing group and a functional handle on the α -position of the thiophene for subsequent palladium catalyzed cross coupling reactions. The lack of β -substituents on the BODIPY moiety is expected to greatly benefit the overall planarity of the molecule due to the limited steric interactions that often force a twist between the thiophene and BODIPY cap.⁷ This molecule is synthesized through Liebeskind-Srogl coupling between 8-

^a Department of Chemistry, University of Massachusetts, Amherst, Massachusetts 01003, United States. Fax: +1-413-545-4490; E-mail: thai@chem.umass.edu


^b Université de Bordeaux, CNRS, IMS UMR 5218, Institut Polytechnique de Bordeaux, ENSCBP, 33607 Pessac, France.; E-mail: guillaume.wantz@ims-bordeaux.fr

[†] Electronic Supplementary Information (ESI) available: Detailed synthetic procedures, NMR spectra, cyclic voltammograms, OFET device preparation procedure and output and transfer characteristics, photovoltaic device preparation procedure and related data. See DOI: 10.1039/b000000x/

Table 1. Optical and electrochemical properties of synthesized molecules

	$\lambda_{\max}^{\text{solution}}$ [nm] (□ [x10 ⁴ M ⁻¹ cm ⁻¹]) ^a	$\lambda_{\max}^{\text{film}}$ [nm] (λ _{onset} ^{film} [nm]) ^b	E_g^{opt} [eV] ^c	E^{ox} [V] ^d	HOMO [eV] ^e	E^{red} [V] ^d	LUMO [eV] ^f
BDP-BDT	518 (6.2)	532 (717)	1.73	0.60	-5.40	-0.91	-3.79
BDP-CPDT	516 (7.6)	530 (805)	1.54	0.36	-5.16	-0.98	-3.82
BDP-DTP	516 (2.5)	532 (845)	1.47	0.34	-5.14	-1.06	-3.74

^a Measured in chlorobenzene solutions; ^b Determined from thin films spun cast from dichloromethane solutions and annealed at 150°C; ^c $E_g^{\text{opt}} = 1240/\lambda_{\text{onset}}^{\text{film}}$; ^d Determined from the onset of oxidation and reduction extracted from cyclic voltammograms measured in anhydrous dichloromethane with 0.1M Bu₄NPF₆ as the supporting electrolyte and corrected with respect to the Fc/Fc⁺ redox couple; ^e HOMO = $-(E^{\text{ox}} + 4.8)$; ^f LUMO = $-(E^{\text{red}} + 4.8)$;

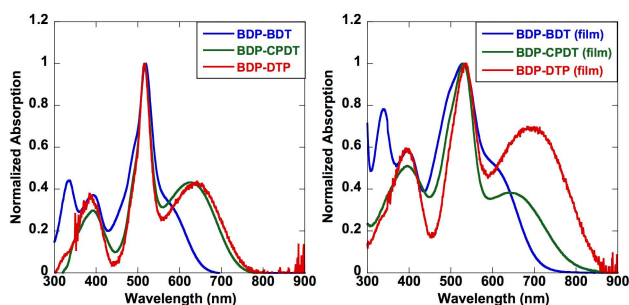**Fig. 1** Solution (left) and thin film (right) absorption spectra of **BDP-BDT**, **BDP-CPDT** and **BDP-DTP**. Solution spectra are from chlorobenzene solvent.

(thiomethyl)-BODIPY and 2-bromo-3-hexylthiophene-5-boronic acid.⁸ Stille coupling between the bistannylated donors and the previously synthesized terminal unit afforded the targeted molecules in good yields. For detailed syntheses and characterization, refer to the ESI.[†]

Donor incorporation through the α and β positions of the BODIPY core is known for extending conjugation and, in turn, red shifting absorption and reducing the band gap of the resulting system. However, conjugation through the *meso* position does not typically provide the same dramatic shift in absorption due to minimal communication between the core and terminal BODIPY in the ground state.⁹ Consequently, through selective tuning of the core, a system possessing a predictable and well-defined absorption profile with significant absorbance within the visible region of the solar spectrum can be synthesized with ease. This feature is important for tuning the absorption properties of the acceptor to complement the donor material with which it is paired in BHJ devices.

Fig. 1 shows the UV-visible absorption spectra for chlorobenzene solutions and thin films spun from dichloromethane solutions; the optical properties are summarized in Table 1. The three molecules exhibit an absorption maximum that is characteristic of the π - π^* transition in the BODIPY moiety,¹⁰ with an extinction coefficient on the order of 10⁴ M⁻¹ cm⁻¹ (Table 1). This absorption slightly red shifts in thin films. All molecules also exhibit a lower energy shoulder that is attributed to an intramolecular charge transfer process, as its position in both the solution and solid states varies with the donor strength of the core moiety. While this band exists as a shoulder in **BDP-BDT**, both **BDP-CPDT** and **BDP-DTP** possess significantly red shifted peaks with absorption onsets at 805 and 845 nm respectively. The significant shift in the latter two molecules is attributed to the enhanced donor strength of the core moiety.¹¹ The optical band gaps for these molecules were estimated from the absorption onset in thin films (Table 1).

Next, the electrochemical properties of the molecules were examined using cyclic voltammetry.¹² Each molecule shows amphoteric

behavior, exhibiting two reversible oxidations and at least one reduction (Figure S1). The onset of the first oxidation potential for **BDP-CPDT** and **BDP-DTP** are very similar, leading to comparable HOMO energy levels (Table 1). Decreasing the donor strength of the core moiety stabilized the HOMO energy level, as the weakest donor (**BDP-BDT**) possesses the most stable HOMO (-5.40 eV). E^{red} values are similar throughout the series, indicating the reduction of the BODIPY moiety within the molecule is relatively unaffected by the donor strength of the core moiety. Since each of these molecules possesses a LUMO significantly lower than that of P3HT, exciton dissociation is thermodynamically possible, allowing them to be considered as candidates for acceptors in BHJ devices.

To investigate the charge transport properties of these molecules, bottom contact organic field effect transistors (OFET) were fabricated. Output and transfer characteristics are displayed and summarized in the ESI.[†] All molecules exhibit only n-type characteristics with mobilities on the order of 10⁻⁵ cm² V⁻¹ s⁻¹ (Table S1). Of the devices, BDP-CPDT exhibited the highest electron mobility (5.77x10⁻⁵ cm² V⁻¹ s⁻¹), while that of BDP-BDT was the lowest (3.30x10⁻⁵ cm² V⁻¹ s⁻¹). Although the directionality of charge transport in OPV devices and OFET devices are orthogonal, the consistent n-type transport in these BODIPY-capped molecules does suggest that this functionality could be a promising building block of low band gap, small molecule acceptors for OPVs.

Inverted OPV devices were fabricated with the architecture ITO/ZnO/P3HT:acceptor (40 nm)/MoO₃ (7 nm)/Ag (100 nm). The active layer was spun cast from 15 mg mL⁻¹ solutions in *o*-dichlorobenzene (*o*-DCB). An optimal D:A ratio was determined to be 1:1.5 for each acceptor (ESI[†]) with **BDP-BDT**, **BDP-CPDT** and **BDP-DTP** yielding efficiencies of 1.21%, 1.02% and 0.84%, respectively. To assess whether the light absorption characteristics at wavelengths complementary to that of P3HT, contribute to the overall efficiency, we obtained the external quantum efficiency (EQE) for these devices. EQE measurements show that the devices containing acceptors with red shifted charge transfer bands (**BDP-CPDT**, **BDP-DTP**) significantly benefit from the acceptor absorption above 650 nm. The weaker

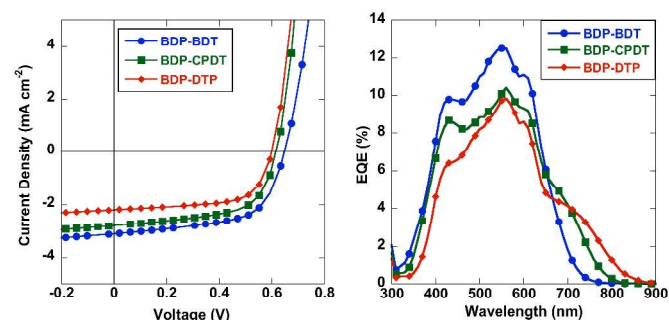
**Fig. 2** J - V curves (left) and EQE spectra (right) of devices with various acceptors where the P3HT:acceptor ratio is 1:1.5.

Table 2. Photovoltaic cell performance (ITO/ZnO/P3HT:acceptor (1:1.5)/MoO₃/Ag) with various amounts of CN solvent additive

Acceptor	CN [vol%]	V _{oc} [V]	J _{sc} [mA cm ⁻²]	FF	PCE [%]
BDP-BDT	0	.65	3.09	.60	1.21
	1	.39	2.73	.30	.33
	3	.57	3.20	.56	1.01
	5	.14	3.03	.26	.11
BDP-CPDT	0	.60	3.28	.61	1.20
	1	.60	3.04	.61	1.11
	3	.62	3.90	.63	1.51
	5	.61	3.67	.63	1.41
BDP-DTP	0	.60	2.18	.65	.84
	1	.56	2.64	.62	.92
	3	.57	3.28	.63	1.18
	5	.57	1.60	.62	.56

Active layers spun cast from 1,2-dichlorobenzene solutions (15mg ml⁻¹) ^a1500 RPM for 60 s and annealed at 150°C for 2 min

performance of the **BDP-DTP** molecule is due to the relatively low J_{sc} (2.18 mA cm⁻²), which is likely due to non-optimal active layer morphology. Use of solvent additives has improved the efficiency of PCBM-based BHJ devices, which has been attributed to the ability of certain solvents to promote PCBM aggregation by selectively solubilizing the acceptor.¹³ Since these acceptors have good solubility in most organic solvents, we decided to use 1-chloronaphthalene (CN) as a solvent additive. The *J-V* curves and EQE spectra are shown in the ESI[†]; the device characteristics are listed in Table 2.

The use of CN as a solvent additive had positive effects on the **BDP-CPDT** and **BDP-DTP** devices, as device efficiency increased to 1.51% and 1.18%, respectively, when 3% CN was added. However, CN had a detrimental effect on **BDP-BDT** devices, yielding decreased V_{oc} and FF values (Table 2). To examine the effect CN on the morphology of the P3HT:**BDP-CPDT** devices, atomic force microscopy (AFM) was used. AFM height and phase images of the P3HT:**BDP-CPDT** active layer are shown in Fig. S9. Adding 3% CN increased the surface roughness from 5.9 nm to 7.2 nm; the additive-based device also shows a much more uniform and well-ordered network, which are desired for efficient charge transport.

In summary, a series of n-type small molecules consisting of a thiophene-based donor core conjugated to a BODIPY cap through the *meso* position were synthesized. These molecules exhibited good visible absorption with a common peak between 530-532 nm in thin films, independent of the donor core. Introduction of a stronger donor (CPDT, DTP) to the core of the molecule led to a significant red shift in the charge transfer band, resulting in an optical band gap of as low as 1.47 eV. Each of the molecules possessed a low-lying LUMO, between -3.7 eV and -3.9 eV, and decent electron mobility, ~10⁻⁵ cm² V⁻¹ s⁻¹, making them potential acceptors for many donor materials. Inverted bulk heterojunction photovoltaic devices were successfully fabricated, combining these molecules with P3HT as the donor. The P3HT:**BDP-BDT** active layer yielded an efficiency of 1.21%. The use of 1-chloronaphthalene as a solvent additive improved device performance in **BDP-CPDT** and **BDP-DTP** based devices, with the best performing cell yielding a PCE of 1.51% (P3HT:**BDP-CPDT** + 3% CN). Further device optimization and morphological studies of the blends are currently underway. Also, we are further investigating the effect of both

core and cap modifications on the electronic properties of the resulting materials for optimal pairing with donors other than P3HT. Through fine-tuning of the molecular structure vs. device performance and morphological characteristics, we hope to achieve a library of BODIPY based electron acceptors with robust electronic properties for OPV applications.

We thank Frédéric Guillain, Lionel Derue, Clémence Lecourtier and Elodie Destouesse of the ELORGA research team of the IMS laboratory at the University of Bordeaux for their help with photovoltaic device fabrication. Support from the U.S. Department of Energy through the EFRC at UMass Amherst (DE-SC0001087). We also thank the National Science Foundation for partial support through the Collaborative Undergraduates Research in Energy (CURE) REU program to WW and the Northeast Alliance for Graduate Education and the Professoriate (NSF9978878) to AMP.

Notes and references

- (a) Z. He, C. Zhong, S. Su, M. Xu, H. Wu and Y. Cao, *Nat. Photonics*, 2012, **6**, 593; (b) C. L. Chochos and S. A. Choulis, *Prog. Polym. Sci.*, 2011, **36**, 1326; (c) Y. Lin, Y. Li and X. Zhan, *Chem. Soc. Rev.*, 2012, **41**, 4245; (d) Y. Li, *Acc. Chem. Res.*, 2012, **45**, 723; (e) L. Huo, S. Zhang, X. Guo, F. Xu, Y. Li and J. Hou, *Angew. Chem. Int. Ed.*, 2011, **50**, 9697; (f) H. Zhou, L. Yang and W. You, *Macromolecules*, 2012, **45**, 607.
- (a) B. C. Thompson and J. M. Frechet, *Angew. Chem. Int. Ed.*, 2008, **47**, 58; (b) T. Liu and A. Troisi, *Adv. Mater.*, 2013, **25**, 1038.
- (a) Y. Zhou, Y. Z. Dai, Y. Q. Zheng, X. Y. Wang, J. Y. Wang and J. Pei, *Chem. Commun.*, 2013, **49**, 5802; (b) J. T. Bloking, X. Han, A. T. Higgs, J. P. Kastrop, L. Pandey, J. E. Norton, C. Risko, C. E. Chen, J.-L. Brédas, M. D. McGehee and A. Sellinger, *Chem. Mater.*, 2011, **23**, 5484; (c) C. L. Chochos, N. Tagmatarchis and V. G. Gregoriou, *RSC Adv.*, 2013, **3**, 7160.
- (a) Y. Zhou, L. Ding, K. Shi, Y. Z. Dai, N. Ai, J. Wang and J. Pei, *Adv. Mater.*, 2012, **24**, 957; (b) Y. Lin, P. Cheng, Y. Li and X. Zhan, *Chem. Commun.*, 2012, **48**, 4773; (c) J. E. Anthony, *Chem. Mater.*, 2011, **23**, 583; (d) A. a. F. Eftaiha, J.-P. Sun, I. G. Hill and G. C. Welch, *J. Mater. Chem. A*, 2013.
- A. C. Benniston and G. Copley, *Phys. Chem. Chem. Phys.*, 2009, **11**, 4124.
- Y. Hayashi, N. Obata, M. Tamaru, S. Yamaguchi, Y. Matsuo, A. Saeki, S. Seki, Y. Kureishi, S. Saito, S. Yamaguchi and H. Shinokubo, *Org. Lett.*, 2012, **14**, 866.
- (a) A. C. Benniston, G. Copley, A. Harriman, D. B. Rewinska, R. W. Harrington and W. Clegg, *J. Am. Chem. Soc.*, 2008, **130**, 7174; (b) C.-C. Chi, Y.-J. Huang and C.-T. Chen, *J. Chin. Chem. Soc.*, 2012, **59**, 305.
- (a) E. Lager, J. Liu, A. Aguilar-Aguilar, B. Z. Tang and E. Pena-Cabrera, *J. Org. Chem.*, 2009, **74**, 2053; (b) E. Pena-Cabrera, A. Aguilar-Aguilar, M. Gonzalez-Dominguez, E. Lager, R. Zamudio-Vazquez, J. Godoy-Vargas and F. Villanueva-Garcia, *Org. Lett.*, 2007, **9**, 3985.
- (a) J. C. Fergie, P. J. Skabara, I. Stibor, F. Vilela and Z. Vobecka, *Chem. Mater.*, 2009, **21**, 1784; (b) B. C. Popere, A. M. Della Pelle, A. Poe, G. Balaji and S. Thayumanavan, *Chem. Sci.*, 2012, **3**, 3093; (c) E. H. A. Beckers, P. A. van Hal, A. Dhanabalan, S. C. J. Meskers, J. Knol, J. C. Hummelen and R. A. J. Janssen, *J. Phys. Chem. A*, 2003, **107**, 6218.
- (a) H. Y. Lin, W. C. Huang, Y. C. Chen, H. H. Chou, C. Y. Hsu, J. T. Lin and H. W. Lin, *Chem. Commun.*, 2012, **48**, 8913; (b) S. Yin, V. Leen, C. Jackers, D. Beljonne, B. Van Averbeke, M. Van der Auweraer, N. Boens and W. Dehaen, *Chem. Eur. J.*, 2011, **17**, 13247.
- D. Collado, J. Casado, S. Rodriguez Gonzalez, J. T. Lopez Navarrete, R. Suau, E. Perez-Inestrosa, T. M. Pappenfus and M. M. Raposo, *Chem. Eur. J.*, 2011, **17**, 498.
- C. M. Cardona, W. Li, A. E. Kaifer, D. Stockdale and G. C. Bazan, *Adv. Mater.*, 2011, **23**, 2367.
- (a) M. T. Dang, L. Hirsch and G. Wantz, *Adv. Mater.*, 2011, **23**, 3597; (b) J. Peet, A. J. Heeger and G. C. Bazan, *Acc. Chem. Res.*, 2009, **42**, 1700; (c) A. Facchetti, *Chem. Mater.*, 2011, **23**, 733.