


Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the RSC Publishing peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, which is prior to technical editing, formatting and proof reading. This free service from RSC Publishing allows authors to make their results available to the community, in citable form, before publication of the edited article. This *Accepted Manuscript* will be replaced by the edited and formatted *Advance Article* as soon as this is available.

To cite this manuscript please use its permanent Digital Object Identifier (DOI®), which is identical for all formats of publication.

More information about *Accepted Manuscripts* can be found in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics contained in the manuscript submitted by the author(s) which may alter content, and that the standard [Terms & Conditions](#) and the [ethical guidelines](#) that apply to the journal are still applicable. In no event shall the RSC be held responsible for any errors or omissions in these *Accepted Manuscript* manuscripts or any consequences arising from the use of any information contained in them.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

The energy transfer and the effect of doped Mg^{2+} in $\text{Ca}_3\text{Sc}_2\text{Si}_3\text{O}_{12}:\text{Ce}^{3+}$, Pr^{3+} phosphor for white LEDs

Jun Qiao,^{a,b} Jiahua Zhang,^{*a} Xia Zhang,^a Zhendong Hao,^a Yongfu Liu,^a and Yongshi Luo^a

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

The energy transfer (ET) and luminescence properties in the Ce^{3+} and Pr^{3+} co-activated $\text{Ca}_3\text{Sc}_2\text{Si}_3\text{O}_{12}$ (CSS) silicate garnet are studied in our work. The addition of Pr^{3+} exhibits a red emission around 610 nm in the green phosphor CSS: Ce^{3+} , but the amount of Pr^{3+} incorporated into the phosphor is very limited due to the charge mismatch when Pr^{3+} substitutes for Ca^{2+} in CSS. In order to promote Pr^{3+} incorporation into CSS lattices to enhance the red emission component, the addition of Mg^{2+} incorporated into Sc^{3+} site is performed to compensate the residual positive charge caused by the substitution of Pr^{3+} for Ca^{2+} in CSS. Finally, a white LED with color rendering index (CRI) of 80 and correlated color temperature (CCT) of 8715 K is obtained by combining the single CSS: 0.05 Ce^{3+} , 0.01 Pr^{3+} , 0.3 Mg^{2+} phosphor with a blue-emitting InGaN LED chip.

1. Introduction

White light emitting diodes (LEDs) are considered to be a promising candidate for the future lighting system because of their higher efficiency, longer lifetime, and lack of requirement for pollutants compared with the conventional light sources such as incandescent lamps or fluorescent lamps.^{1,2} Until now, the most widely used commercial white LEDs are fabricated by combining high performance blue-emitting InGaN chip with $\text{Y}_3\text{Al}_5\text{O}_{12}:\text{Ce}^{3+}$ (YAG: Ce^{3+}) yellow emitting aluminate garnet phosphor that exhibits an emission band peaking at 530 nm with a shoulder at 575 nm, originated from $5d \rightarrow {}^2F_{7/2}$, ${}^2F_{5/2}$ transitions of Ce^{3+} , respectively.^{3,4} YAG: Ce^{3+} has a high converting efficiency, but the deficient red emitting component leads to the CRI of the white LEDs below 80.^{5,6}

To resolve this problem, the method of blending YAG: Ce^{3+} with red emitting phosphors has been proposed. Many studies have therefore been devoted to the development of high performance red phosphors, such as $\text{M}_2\text{Si}_5\text{N}_8:\text{Eu}^{2+}$ ($\text{M} = \text{Ca}, \text{Sr}, \text{Ba}$),⁷ $\text{CaAlSiN}_3:\text{Eu}^{2+}$,⁸ and $\text{Lu}_2\text{CaMg}_2\text{Si}_3\text{O}_{12}:\text{Ce}^{3+}$.⁹ The drawback of phosphor blend is fluorescence reabsorption that results in loss of luminous efficiency. Hence, full color emitting single phase phosphors are expected. The attempt to enhance red emission component in YAG: Ce^{3+} was performed by co-doping Pr^{3+} on Y^{3+} site to generate a red emission line around 610 nm, originated from ${}^1D_2 \rightarrow {}^3H_4$ transition of Pr^{3+} through $\text{Ce}^{3+} \rightarrow \text{Pr}^{3+}$ ET.⁶ A new yellow-emitting $\text{Ba}_{0.93}\text{Eu}_{0.07}\text{Al}_2\text{O}_4$ phosphor with sufficient red component, very good thermal stability was also synthesized by Xufan Li et al. Warm-white emissions with CCT < 4000 K and CRI > 80 were readily achieved when combining this phosphor with a blue light-emitting diode (440–470 nm).¹⁰

Recently, Yasuo Shimomura et al.¹¹ reported a novel green emitting silicate garnet phosphor $\text{Ca}_3\text{Sc}_2\text{Si}_3\text{O}_{12}:\text{Ce}^{3+}$ (CSS: Ce^{3+})

suitable for blue LED excitation. In this host lattices, Ce^{3+} substitution for the dodecahedral Ca^{2+} site is suggested based on the results of extended X-ray absorption fine structure (EXAFS) analysis. It was also found that the emission band appears a remarkable red shift if codoping Mg^{2+} to replace Sc^{3+} , being able to modify CSS: Ce^{3+} to be a yellow emitting phosphor $\text{Ca}_3(\text{Sc}_{2-b}\text{Mg}_b)\text{Si}_3\text{O}_{12}:\text{Ce}^{3+}$ ($0 \leq b \leq 1$).¹² In addition, vacuum ultraviolet (VUV) spectroscopy of CSS doped with Pr^{3+} in Ca^{2+} site has been studied for searching novel fast emitting scintillator by K. V. Ivanovskikh et al.¹³ The addition of Mg^{2+} in Sc^{3+} site is also performed to improve the properties of this novel fast emitting scintillator.¹⁴

In this paper, we investigate the ET from Ce^{3+} to Pr^{3+} and the effect of addition of Mg^{2+} on the luminescence properties of phosphor CSS: Ce^{3+} , Pr^{3+} . A blue-based white LED with CRI of 80 and CCT of 8715 K is obtained by using the single phase CSS: 0.05 Ce^{3+} , 0.01 Pr^{3+} , 0.3 Mg^{2+} phosphor, demonstrating its potential application in white LEDs.

2. Experimental

2.1. Materials and synthesis

The phosphors $\text{Ca}_3\text{Sc}_2\text{Si}_3\text{O}_{12}:\text{0.05Ce}^{3+}, x\text{Pr}^{3+}$ (CSS: 0.05 Ce^{3+} , $x\text{Pr}^{3+}$) ($x=0-0.06$), $\text{Ca}_3(\text{Sc}_{2-y}\text{Mg}_y)\text{Si}_3\text{O}_{12}:\text{0.01Pr}^{3+}$ (CSS: 0.01 Pr^{3+} , $y\text{Mg}^{2+}$), $\text{Ca}_3(\text{Sc}_{2-y}\text{Mg}_y)\text{Si}_3\text{O}_{12}:\text{0.05Ce}^{3+}$ (CSS: 0.05 Ce^{3+} , $y\text{Mg}^{2+}$) and $\text{Ca}_3(\text{Sc}_{2-y}\text{Mg}_y)\text{Si}_3\text{O}_{12}:\text{0.05Ce}^{3+}, \text{0.01Pr}^{3+}$ (CSS: 0.05 Ce^{3+} , 0.01 Pr^{3+} , $y\text{Mg}^{2+}$) ($y=0-0.3$) were synthesized by conventional solid-state reaction. The constituent oxides or carbonates CaCO_3 , Sc_2O_3 , SiO_2 , MgO , CeO_2 , and $\text{Pr}(\text{NO}_3)_3$ were employed as the raw materials. The mixtures of raw materials were sintered in a tubular furnace at 1350 °C for 4 h in reductive atmosphere (5% $\text{H}_2 + 95\% \text{N}_2$).

2.2. Measurements and characterization

The photoluminescence (PL) and photoluminescence excitation (PLE) spectra were measured using a FS920 spectrometer (Edinburgh Instruments, U. K.). The diffuse reflectance (DR) spectra were measured using HITACHI F-7000 spectrometer.

The fluorescence decay curves of Ce^{3+} were measured by a FL920 Fluorescence Lifetime Spectrometer (Edinburgh Instruments, Livingston, UK) and a hydrogen flash lamp (nF900, Edinburgh Instruments). In the measurements of fluorescence decay of Pr^{3+} , an optical parametric oscillator (OPO) is used as an excitation source. The signal is detected by a Tektronix digital oscilloscope (TDS 3052). Powder X-ray diffraction (XRD) data were collected using Cu-K α radiation ($\lambda=1.54056$ Å) on a Bruker D8 Advance diffractometer. The chromaticity coordinates, color rendering index (CRI) and the correlated color temperature (CCT) of white LEDs were measured using Ocean Optics USB4000 Spectrometer.

3. Results and discussion

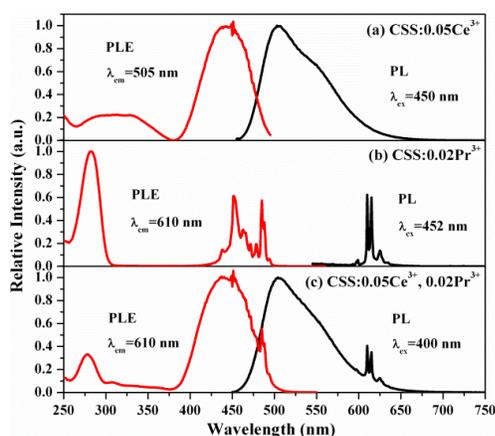


Fig. 1 PLE and PL spectra for CSS: 0.05Ce³⁺ (a), CSS: 0.02Pr³⁺ (b) and CSS: 0.05Ce³⁺, 0.02Pr³⁺ (c).

Fig. 1 shows the PLE and PL spectra for CSS: 0.05Ce³⁺ (a), CSS: 0.02Pr³⁺ (b) and CSS: 0.05Ce³⁺, 0.02Pr³⁺ (c). CSS: 0.05Ce³⁺ exhibits a typical green PL band with a peak at 505 nm and a shoulder around 540 nm, originated from the transitions from 5d to ²F_{5/2} and ²F_{7/2} of Ce³⁺, respectively.¹¹ Meanwhile, the PLE spectrum for the green emission exhibits an intense excitation band around 450 nm, well matching the emitting wavelength of the blue InGaN LEDs. The Pr³⁺ singly doped CSS exhibits a red emission around 610 nm, originated from ¹D₂→³H₄ transition of Pr³⁺. The PLE spectrum for the red emission of Pr³⁺ includes two bands. The band in the range of 430 to 500 nm is attributed to the transitions from the ³H₄ ground state to the upper triply split ³P_J (J=0, 1, 2) levels and the ¹I₆ level, and another band peaked around 285 nm is ascribed to the electronic transitions from the ³H₄ level to the 4f¹5d band.^{15,16} In CSS: 0.05Ce³⁺, 0.02Pr³⁺, the PL spectrum upon Ce³⁺ excitation at 400 nm exhibits not only the Ce³⁺ emission band around 505 nm but also the Pr³⁺ emission around 610 nm, and the typical PLE band of Ce³⁺ accounts for the dominant part in the PLE spectrum around 450nm by monitoring at 610 nm. These features prove that there is obvious ET from Ce³⁺ to Pr³⁺ in Ce³⁺ and Pr³⁺ co-doped sample. The occurrence of ET can be clearly understood as noticing the spectral overlap between the Ce³⁺ emission band in CSS: 0.05Ce³⁺ and the Pr³⁺

excitation band in CSS: 0.02Pr³⁺.

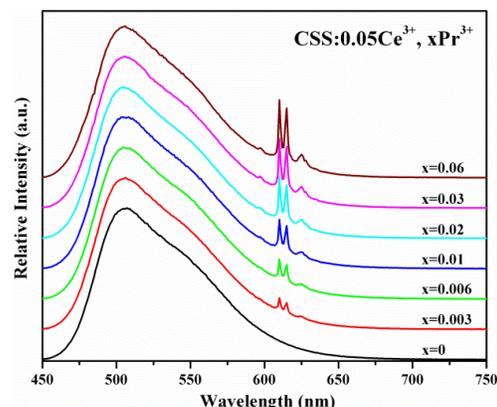


Fig. 2 Normalized PL spectra for CSS: 0.05Ce³⁺, xPr³⁺ under 400 nm excitation.

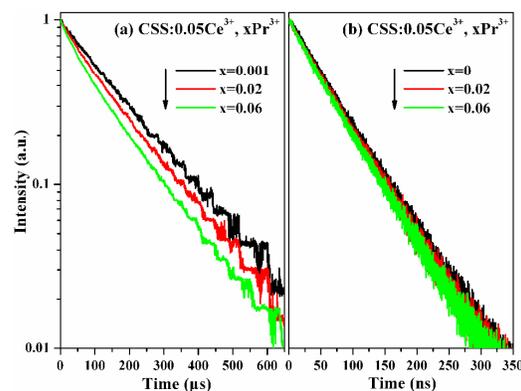


Fig. 3 Photoluminescence decay curves of Pr³⁺ (excited at 610 nm, monitored at 714 nm) (a) and Ce³⁺ (excited at 450 nm, monitored at 505 nm) (b) in CSS: 0.05Ce³⁺, xPr³⁺.

Fig. 2 shows the normalized PL spectra for CSS: 0.05Ce³⁺, xPr³⁺ by 400 nm excitation. Considering that the excitation wavelength of 400 nm can only directly excite Ce³⁺ rather than Pr³⁺, the excitation of Pr³⁺ must be performed completely through Ce³⁺→Pr³⁺ ET. It is observed that the intensity of Pr³⁺ emission obviously increases with increasing the nominal Pr³⁺ content in the raw material, reflecting the enhanced ET efficiency with increasing the concentration of Pr³⁺ in CSS. In contrast to the phenomena that remarkable concentration quenching takes place for Pr³⁺ concentration at 0.06 in Y₃Al₅O₁₂,¹⁷ the intensity of Pr³⁺ emission continuously increases with increasing the Pr³⁺ content to 0.06 in the raw material of CSS, as shown in Fig. 2. Considering the fact that Ce³⁺ in CSS has a limited solubility around mole 1.1% due to the charge mismatch when Ce³⁺ substitutes for Ca²⁺, as reported by Yasuo Shimomura et al,¹¹ Pr³⁺ may meet the same situation. We therefore infer that the real concentration of Pr³⁺ incorporated in CSS lattices is lower than both the nominal concentration and the quenching concentration. This viewpoint is supported by the observation of slightly shortened Pr³⁺ ¹D₂ lifetimes at higher concentrations, as shown in Fig. 3(a). The decay curves of Pr³⁺ ¹D₂ state for different Pr³⁺ nominal contents are measured by monitoring ¹D₂→³H₅ emission of Pr³⁺ at 714 nm upon ³H₄→¹D₂ pulsed excitation at 610 nm. In addition, the fluorescence decay curves of Ce³⁺ monitored at 505 nm upon pulsed excitation at 450 nm are presented in Fig. 3(b).

Compared with fluorescence lifetime (69 ns) of Ce^{3+} in absence of Pr^{3+} , the tiny variation about that of Ce^{3+} in presence of Pr^{3+} indicates the ET efficiency from Ce^{3+} to Pr^{3+} is very limited due to low Pr^{3+} concentration in CSS. The longer average distance

between Ce^{3+} and Pr^{3+} results in weak interaction between them, so the ET from Ce^{3+} to Pr^{3+} is not very efficient.

In order to explore the approach for enhancing the Pr^{3+} concentration in CSS, we have tentatively prepared CSS: 0.05Ce^{3+} , 0.01Pr^{3+} , $y\text{Mg}^{2+}$ with a fixed nominal Pr^{3+} content at 0.01 and various nominal Mg^{2+} content y from 0 to 0.3, in which Mg^{2+} is incorporated into CSS by substituting the Sc^{3+} site due to the ionic radius of Mg^{2+} is close to that of Sc^{3+} .¹²

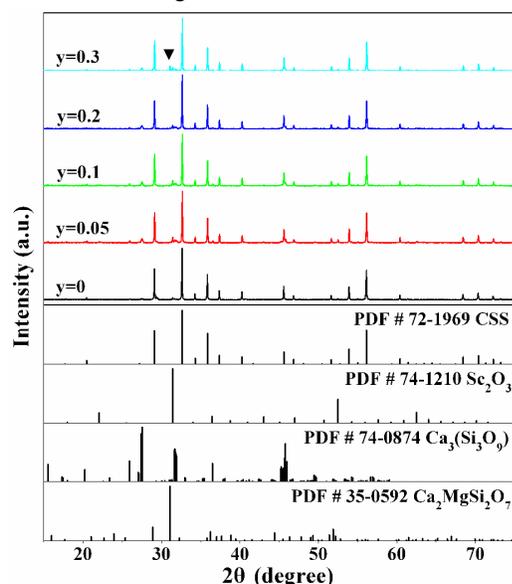


Fig. 4 XRD patterns for phosphors with nominal compositions of $\text{Ca}_{2.94}\text{Sc}_{2-y}\text{Mg}_y\text{Si}_3\text{O}_{12}: 0.05\text{Ce}^{3+}, 0.01\text{Pr}^{3+}$ ($y=0-0.3$).

Fig. 4 shows the XRD patterns for the phosphors with nominal compositions of $\text{Ca}_{2.94}\text{Sc}_{2-y}\text{Mg}_y\text{Si}_3\text{O}_{12}: 0.05\text{Ce}^{3+}, 0.01\text{Pr}^{3+}$ ($y=0-0.3$). The primary phase in all of these samples is CSS garnets (JCPDF No. 72-1969) with a few by-products of Sc_2O_3 phase (JCPDF No. 74-1210) and $\text{Ca}_3(\text{Si}_3\text{O}_9)$ phase (JCPDF No. 74-0874). In addition, when the nominal content of Mg^{2+} reaches to 0.3 in the raw material, a by-product $\text{Ca}_2\text{MgSi}_2\text{O}_7$ phase (JCPDF No. 35-0592) emerges in the sample due to the excessive Mg^{2+} in the raw material cannot be incorporated into the CSS garnet phosphor. Fortunately, the by-products do not affect the luminescence properties of the phosphor.¹²

Fig. 5 shows the PL spectra for CSS: $0.05\text{Ce}^{3+}, 0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ under 400 nm excitation (a) and CSS: $0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ under 452 nm excitation (b). The PL spectra of Ce^{3+} in the phosphors containing Mg^{2+} are moved toward longer wavelength with increasing Mg^{2+} content in the raw material. As reported by Yasuo Shimomura et al, this phenomenon is likely caused by the increase in amount of the activator.¹² Some interaction among the activators probably modified the luminescence characteristics. This conclusion can be also demonstrated in the DR spectra for CSS: $0.05\text{Ce}^{3+}, y\text{Mg}^{2+}$ (Fig. 6(a)), in which the absorption around 450 nm that is attributed to the typical $4f \rightarrow 5d$ transition of Ce^{3+} in CSS enhances with increasing Mg^{2+} content, indicating that Mg^{2+} substitution for Sc^{3+} can promote Ce^{3+} incorporation into

CSS lattices by compensating the charge mismatch between Ce^{3+} and Ca^{2+} .

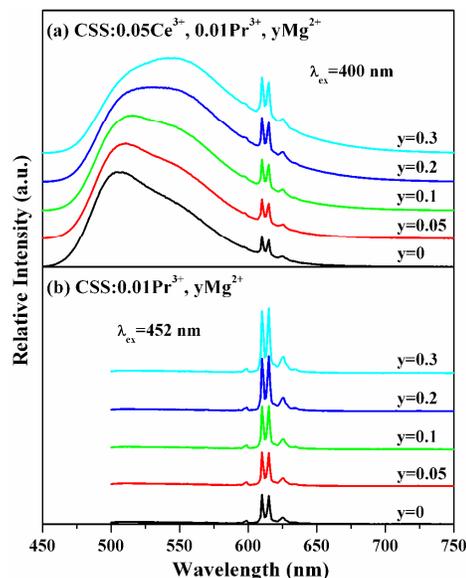


Fig. 5 PL spectra for CSS: $0.05\text{Ce}^{3+}, 0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ under 400 nm excitation (a) and CSS: $0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ under 452 nm excitation (b).


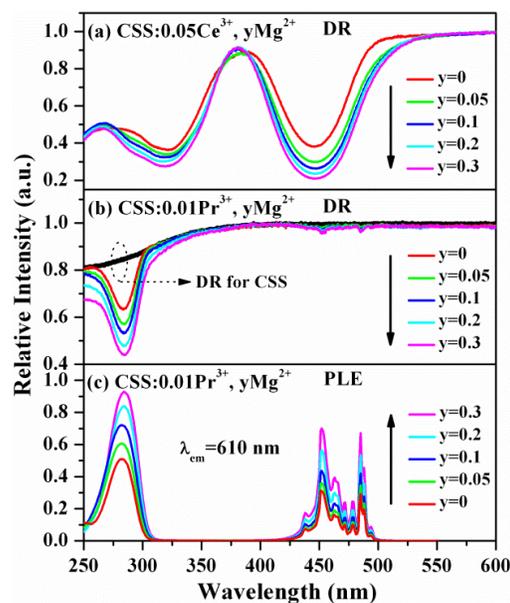


Fig. 6 DR spectra for CSS: $0.05\text{Ce}^{3+}, y\text{Mg}^{2+}$ (a), CSS: $0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ (b) and PLE spectra for CSS: $0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ (c).

In contrast, the PL spectra of Pr^{3+} in these samples are located around 610 nm without any red shift with increasing Mg^{2+} content, due to the Pr^{3+} emission around 610 nm is originated from $^1\text{D}_2 \rightarrow ^3\text{H}_4$ transition which is hardly affected by local environment. Nonetheless, the intensity of Pr^{3+} emission around 610 nm is markedly enhanced in the spectra for not only CSS: $0.05\text{Ce}^{3+}, 0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ but also CSS: $0.01\text{Pr}^{3+}, y\text{Mg}^{2+}$ by increasing Mg^{2+} content. In view of the effect of Mg^{2+} in CSS: $0.05\text{Ce}^{3+}, y\text{Mg}^{2+}$, we infer that the enhancement of Pr^{3+} emission is ascribed to the increasing Pr^{3+} concentration in CSS, Mg^{2+} substitution for Sc^{3+} can compensate the residual positive charge caused by Pr^{3+} substitution for Ca^{2+} .

Fig. 6(b) and 6(c) show the DR spectra and PLE spectra ($\lambda_{\text{em}}=610$ nm) for CSS: 0.01Pr³⁺, yMg²⁺, respectively. The bold black line in Fig. 6(b) represents the DR spectrum for undoped CSS. The slender absorptions in the range of 430 to 500 nm are attributed to the transitions of Pr³⁺ from the ³H₄ ground state to the upper triply split ³P_J (J=0, 1, 2) levels and the ¹I₆ level. The absorption around 285 nm is ascribed to the electronic transition of Pr³⁺ from the ³H₄ level to the 4f⁴5d band.^{15,16} With increasing Mg²⁺ content in the raw material, the absorptions, which are correlated to the amount of Pr³⁺ in CSS, are gradually enhanced, indicating that the Pr³⁺ concentration is increased by the incorporation of Mg²⁺ into CSS lattices. This conclusion accords with our previous inference. The PLE bands ($\lambda_{\text{em}}=610$ nm) for CSS: 0.01Pr³⁺, yMg²⁺ are also located around 285 nm and in the range of 430 to 500 nm, well consistent with their DR bands, as

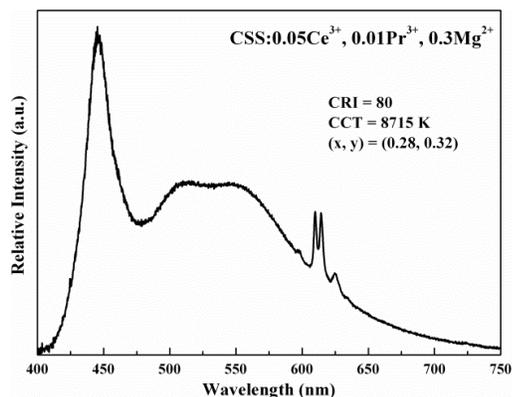

shown in Fig. 6(c).

Fig. 7 Emission spectrum for the white LED fabricated using the single phosphor with nominal composition of CSS: 0.05Ce³⁺, 0.01Pr³⁺, 0.3Mg²⁺ and an InGaN LED ($\lambda_{\text{ex}}=450$ nm) chip. The current is 20 mA.

To evaluate the chromaticity characteristics of white light generated from our present phosphor under blue light excitation, a white LED is fabricated. As shown in Fig. 7, when the single phosphor with nominal composition of CSS: 0.05Ce³⁺, 0.01Pr³⁺, 0.3Mg²⁺ is excited by a blue InGaN LED (450 nm) chip, a white LED with CRI of 80, CCT of 8715 K and chromaticity coordinates of (0.28, 0.32) is obtained at the forward current of 20 mA. The results of this work demonstrate the potential application of the single CSS: 0.05Ce³⁺, 0.01Pr³⁺, 0.3Mg²⁺ phosphor in blue-based white LEDs. However, this white LED needs more red emission component to be excellent lighting source. In order to improve the performance of this white LED to obtain ideal lighting source with higher CRI and lower CCT, further exploration to enhance the red emission of this phosphor is necessary.

4. Conclusions

In summary, we investigated the Ce³⁺→Pr³⁺ ET in the silicate garnet CSS. The luminescence spectra exhibit a red Pr³⁺ emission around 610 nm through the Ce³⁺→Pr³⁺ ET upon excitation at 400 nm. The intensity of Pr³⁺ emission continuously increases with increasing the Pr³⁺ content to 0.06 in the raw material, due to the limited increasing concentration of Pr³⁺ in CSS enhances the ET efficiency from Ce³⁺ to Pr³⁺. The addition of Mg²⁺ can not only

increase Ce³⁺ concentration in CSS to make PL spectra move toward longer wavelength, but also promote Pr³⁺ incorporation into CSS lattices to enhance the Pr³⁺ emission. The luminescence spectra of CSS: 0.05Ce³⁺, 0.01Pr³⁺ containing Mg²⁺ were modified to contain enriched longer wavelength emissive component so as to generate white light. A white LED with CRI of 80, CCT of 8715 K and chromaticity coordinates of (0.28, 0.32) was fabricated by combining the single CSS: 0.05Ce³⁺, 0.01Pr³⁺, 0.3Mg²⁺ phosphor with an InGaN LED (450 nm) chip. Our works demonstrate the promising application of this phosphor in blue-based white LEDs. In order to improve the performance of this white LED to obtain ideal lighting source, further exploration is needed to enrich the red emission of this phosphor.

Acknowledgments

This work was supported by the National Natural Science Foundation of China (10834006, 51172226, 61275055, 10904141, and 10904140).

Notes and references

- ^a Key Laboratory of Luminescence and Application, Changchun Institute of Optics, Fine Mechanics and Physics, Chinese Academy of Sciences, Changchun, China.
E-mail: zhangjh@ciomp.ac.cn; Tel./Fax: +86-431-8617-6317
- ^b University of Chinese Academy of Sciences, Beijing 100039, P. R. China
- 1 S. Nakamura, T. Mukai and M. Senoh, *Appl. Phys. Lett.*, 1994, **64**, 1687.
 - 2 E. F. Schubert and J. K. Kim, *Science*, 2005, **308**, 1274.
 - 3 K. Bando, K. Sakano, Y. Noguchi and Y. Shimizu, *J. Light Visual Environ.*, 1998, **22**, 2.
 - 4 G. Blasse and A. Bril, *Appl. Phys. Lett.*, 1967, **11**, 53.
 - 5 Y. Chen, M. Gong, G. Wang and Q. Su, *Appl. Phys. Lett.*, 2007, **91**, 071117.
 - 6 H. S. Jang, W. B. Im, D. C. Lee, D. Y. Jeon and S. S. Kim, *J. Lumin.*, 2007, **126**, 371.
 - 7 Y.Q. Li, J.E.J. van Steen, J.W.H. van Kreveld, G. Botty, A.C.A. Delsing, F.J. DiSalvo, G. de With and H.T. Hintzen, *J. Alloys. Compd.*, 2006, **417**, 273.
 - 8 K. Uheda, N. Hirosaki, Y. Yamamoto, A. Naito, T. Nakajima and H. Yamamoto, *Electrochem. Solid-State Lett.*, 2006, **9**, H22.
 - 9 A. A. Setlur, W. J. Heward, Y. Gao, A. M. Srivastava, R. G. Chandran and M. V. Shankar, *Chem. Mater.*, 2006, **18**, 3314.
 - 10 X. F. Li, J. D. Budai, F. Liu, J. Y. Howe, J.H. Zhang, X. J. Wang, Z. J. Gu, C. J. Sun, R. S. Meltzer and Z.W. Pan, *Light: Sci. & Appl.*, 2013, **2**, e50.
 - 11 Y. Shimomura, T. Honma, M. Shigeiwa, T. Akai, K. Okamoto and N. Kijima, *J. Electrochem. Soc.*, 2007, **154**, J35.
 - 12 Y. Shimomura, T. Kurushima, M. Shigeiwa and N. Kijima, *J. Electrochem. Soc.*, 2008, **155**, J45.
 - 13 K.V. Ivanovskikh, A. Meijerink, F. Piccinelli, A. Speghini, E. I. Zinin, C. Ronda and M. Bettinelli, *J. Lumin.*, 2010, **130**, 893.
 - 14 K. V. Ivanovskikh, A. Meijerink, F. Piccinelli, A. Speghini, C. Ronda and M. Bettinelli, *ECS J. Solid State Sci. Technol.*, 2012, **1**, R127.
 - 15 R. Marin, G. Sponchia, P. Riello, R. Sulcis and F. Enrichi, *J. Nanopart. Res.*, 2012, **14**, 886.
 - 16 R. Piramidowicz, K. Lawniczuk, M. Nakielska, J. Sarniecki and M. Malinowski, *J. Lumin.*, 2008, **128**, 708.
 - 17 L. Wang, X. Zhang, Z.D. Hao, Y.S. Luo, J.H. Zhang and X.J. Wang, *J. Appl. Phys.*, 2010, **108**, 093515.

Graphical Abstract

A white LED is obtained by combining the single CSS: 0.05Ce³⁺, 0.01Pr³⁺, 0.3Mg²⁺ phosphor with a blue-emitting InGaN LED chip.

