

Nanoscale

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Detection of High-Energy Compounds Using Photoluminescent Silicon Nanocrystal Based Paper Sensors

Christina M. Gonzalez,^a Muhammad Iqbal,^a Mita Dasog,^a Davin Piercey,^c Ross Lockwood,^d Thomas M. Klapötke,^c Jonathan G. C. Veinot^{*ab}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX
DOI: 10.1039/b000000x

Luminescent silicon nanocrystals (Si-NCs) surface functionalized with dodecyl groups were exposed to solutions of nitroaromatic compounds including nitrobenzene, nitrotoluene, and dinitrotoluene. It was found that Si-NC luminescence was quenched upon exposure to nitroaromatics via electron transfer mechanism as indicated by Stern-Volmer analysis. This quenching was exploited and a straightforward paper-based Si-NC sensor was developed. This paper motif was found to be sensitive to solution, vapor, and solid phase nitroaromatics, as well as solution borne RDX and PETN.

Introduction

Of late, sensing high energy materials (*i.e.*, explosives) has received substantial attention because of the obvious importance to security and forensics; detection of these materials is also crucial because many are toxic and pose environmental risks.^{6,7,9} Modern methods for detecting explosives include gas chromatography coupled with mass spectrometry, ion mobility spectrometry, surface enhanced Raman spectroscopy, and energy dispersive X-ray spectroscopy.¹⁰⁻¹³ Unfortunately, all of the methods are infrastructure intensive and cannot be readily implemented in the field or outside a laboratory setting.¹⁴ There is a concerted push to develop sensing technologies that are cost effective. One approach has been to use paper substrates as sensing motifs. For example, paper-based Surface Enhanced Raman Spectroscopy substrates for explosive detection have also been developed.³¹⁻³² In this context, development of complementary techniques for straightforward, rapid, on-site detection is of paramount importance.

^a Department of Chemistry, University of Alberta, Edmonton, Alberta T6G 2G2, Canada Fax: +1-780-492-8231; Tel: +1-780-492-7206; E-mail: jveinot@ualberta.ca

^b NRC National Institute for Nanotechnology, Edmonton, Alberta, T6G 2M9, Canada

^c Department of Chemistry, Energetic Materials Research, Ludwig-Maximilian University, Butenandstr. 5-13 (D) 81377 München, Germany

^d Department of Physics, University of Alberta, Edmonton, Alberta T6G 2G2, Canada

† Electronic Supplementary Information (ESI) available: Experimental details, Si-NCs characterization, fluorescent spectra, solid residue testing and vapor study images. See DOI: 10.1039/b000000x/

An attractive approach toward realizing this goal is the development of fluorescent sensors that respond to these compounds. These sensors are usually comparatively simple, require minimal infrastructure, are cost effective, and exhibit adequate sensitivity as well as response times.⁸ Recently, luminescent nanomaterials (*e.g.*, Cd-based quantum dots (QDs)) have been explored as fluorescent sensors because of their exquisite tunability.^{15,24,25} Freeman and coworkers successfully employed fluorescent, functionalized CdSe/ZnS QDs to detect trace quantities of trinitrotoluene (TNT) and cyclotrimethylenetrinitramine (RDX).⁵ In efforts to render these systems portable and increase their compatibility with field applications, researchers interfaced the active nanomaterials with common filter paper to afford a detection system. Zhang and coworkers coated filter paper with dual-emission CdTe QDs that luminesce different colours in the presence of TNT.³ Similarly, Ma and coworkers used the molecular emitter 8-hydroxyquinoline aluminum and nanospheres to detect 2,4,6-trinitrophenol (TNP).⁴

Quantum dots have the clear advantage over molecule-based emitters that they do not photobleach, however, CdSe and CdTe QDs are toxic.²¹ Furthermore, regulations exist or are pending in numerous jurisdictions that limit their widespread use in industrial and consumer applications – new materials must be explored.²¹ Silicon nanocrystals (Si-NCs) are an attractive alternative material that maintains all the advantages of Cd-based quantum dots (*e.g.*, tailorability and photostability) with the clear benefit of being non-toxic. Content and coworkers showed the photoluminescence of hydride terminated porous silicon films was quenched upon exposure to dinitrotoluene (DNT), TNT, and nitrobenzene (NB) vapors. These quenching processes are believed to occur *via* a reversible electron transfer mechanism or irreversible chemical oxidation depending on the duration of vapor exposure.¹ However, hydride terminated porous silicon surface is readily oxidized upon exposure to air and is fragile, thus making it impractical for field applications. Germanenko and coworkers demonstrated the red luminescence of web-like agglomerated silicon nanocrystals (*d* ~ 5-6 nm) bearing a 1-2 nm oxide surface layer was quenched when exposed to nitroaromatic compounds.² Unfortunately, the luminescence of these materials was not affected by explosives-related compounds NB and mononitrotoluene (MNT) that are common degradation products of nitro class explosives typically found in landmines.²⁶ These

early reports demonstrate the promise of Si-based nanomaterials and suggest photoluminescent Si-NCs could be used as sensors for nitro containing explosives. To the best of our knowledge, no study has been reported that employed well-defined freestanding alkyl terminated surface silicon nanocrystals as a nitroaromatic, nitroamine or nitrate ester explosives detection system.

In this work, we describe the detection of a series of nitroaromatic compounds (*i.e.*, mononitrotoluene (MNT), nitrobenzene (NB), dinitrotoluene (DNT), and trinitrotoluene (TNT)), as well as the nitramine RDX and nitrate ester PETN by exploiting the optical response of non-toxic dodecyl functionalized Si-NCs in solution. We subsequently extend this investigation and outline the fabrication and application of an air stable fluorescent paper detector based upon these particles. This paper-based system showed rapid detection of nitroaromatics, nitroamine, and nitrate esters by luminescent quenching in solution, vapor and solid phase at nanogram levels.

Results and Discussion

Characterization of dodecyl functionalized Si-NCs

Oxide-embedded Si-NCs were obtained from the thermally induced disproportionation of HSQ.¹⁹ After etching with HF, red-emitting, hydride terminated Si-NCs were obtained and immediately functionalized with dodecene *via* thermally induced hydrosilylation as reported previously.¹⁹ Material characterization is summarized in Fig. S1. The FTIR spectrum (Fig. S1A†) shows features characteristic of alkyl terminated surfaces at 2920 cm⁻¹ (C-H stretching) and 1450 cm⁻¹ (-C-H bending) consistent with dodecyl functionalization.²⁰ Features observed at 2110 cm⁻¹ and 1050 cm⁻¹ indicate small amounts of SiH_x and Si-O-Si functionalities, respectively, remain following alkyl modification. The PL spectrum of the dodecyl functionalized Si-NCs in toluene (Fig. S1B†) shows a peak intensity maximum at 643 nm. Morphology of the functionalized Si-NCs was evaluated using transmission electron microscopy (Fig. S1C†) which indicates the particles are pseudospherical with an average diameter of 3.7 ± 0.4 nm (Fig. S1D).

Fluorescence quenching by nitroaromatic compounds

Upon the addition of nitroaromatic compounds (*i.e.*, NB, MNT, and DNT) to solutions of dodecyl functionalized Si-NCs, luminescence was quenched. Fig. 1A shows titration curves of the fluorescence peak intensity of toluene solutions containing 1 mg/mL Si-NCs as a function of DNT concentrations ranging from 0.05 to 25 mM. Consistent with previous reports, the degree of Si-NCs PL quenching was proportional to the concentration of DNT (*i.e.*, higher the DNT concentration, the more efficient the quenching). In addition, no shift in PL maximum or changes in the line shape of the PL spectrum resulted. Similar behaviour is observed in the titration curves for the NB and MNT compounds investigated (Fig. S2A-B†).

To gain a more complete understanding of the quenching behaviour induced by NB, MNT, and DNT on dodecyl functionalized Si-NCs PL data was evaluated using the Stern-Volmer equation:

$$I_0/I = K_{sv}[Q] + 1$$

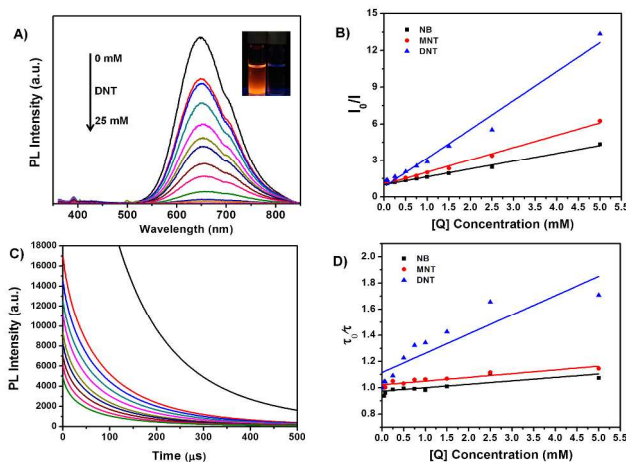


Fig.1 (A) Fluorescence quenching spectra of Si-NCs by increasing concentrations of DNT in solution with an inset showing the quenching effect with 0 and 25 mM DNT atop bench-top UV-lamp. (B) and (D) The Stern-Volmer plots for the quenching efficiencies and PL lifetimes of NB, MNT and DNT at different concentrations. (C) The PL lifetime decays of Si-NCs with increasing concentrations of DNT. The quencher concentrations for all studies can be found in Table S1†.


Where, I_0 and I are the fluorescence intensity in the absence and presence of nitroaromatic compounds, respectively. $[Q]$ is the nitroaromatic compound concentration, and K_{sv} is the fluorescence quenching constant. Fig. 1B shows a linear relationship of I_0/I vs. nitroaromatic compound (NB, MNT, DNT) concentration. In the range of 0.05-5 mM, NB, MNT, and DNT display linear behaviour indicative of the quenching arising from a dynamic process such as an electron transfer.²³ It has been proposed, based upon the correlation of reduction potentials in nitroaromatic compounds, that luminescence quenching of both porous silicon and oxide terminated web-like aggregates of Si-NCs proceeds *via* an electron transfer pathway.^{1,2,22} Suggestions have been made that the electron transfer occurs from the Si nanomaterial conduction band to the vacant π^* orbital of the nitroaromatic compound, resulting in photoluminescence quenching.^{2,27} If this is the case for the present systems, considering the known reduction potentials of NB, MNT, and DNT (*i.e.*, -1.15 V, -1.19 V, and -0.9 V vs NHE in acetonitrile, respectively),^{1,22} the PL quenching efficiency should decrease with redox potential. As such, DNT should be the most efficient quencher of the three tested here. The K_{sv} values determined from the analysis presented in Fig. 1B are 6.44 (mM)⁻¹, 1.01 (mM)⁻¹, and 2.36 (mM)⁻¹ for NB, MNT, and DNT, respectively. This trend supports the hypothesis that quenching is actually occurring *via* an electron transfer mechanism.

To further verify the quenching mechanism is a dynamic process, the PL lifetime of the Si-NCs as a function for each of the nitroaromatic quenchers (*i.e.*, NB, MNT, DNT) concentration in the range of 0.05-5 mM was studied. If the PL lifetime is independent of the quencher concentration, the quenching mechanism is static and is governed by the formation of a ground state nanoparticle-analyte complex.³⁰ Alternatively, if the quenching process is dynamic there will be a decrease in the lifetime because of additional deactivation pathways (*e.g.*, electron transfer) that will shorten the lifetime.³⁰ For the present system, increasing the concentration of the nitroaromatic

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

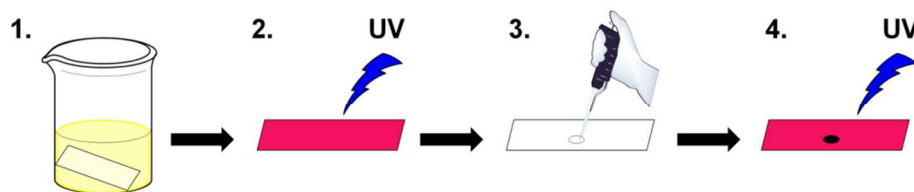

Scheme 1 Schematic representation of the preparation and use of Si-NCs based sensor paper. (1) A piece of filter paper is dip coated in a solution of concentrated Si-NCs, (2) the resulting paper is fluorescent under UV light, (3) nitroaromatic solution is spotted onto the sensing paper, (4) quenching of the spot is observed under UV light.

compound resulted in a decrease of lifetime decays (Fig 1C, Fig. S2C-D†). These results were then plotted as τ_0/τ vs. nitroaromatic compound (NB, MNT, DNT) concentration where τ_0 and τ are the PL lifetimes in the absence and presence of nitroaromatic compounds, respectively (Fig 1D). As expected, DNT was the most efficient lifetime quencher of all nitro compounds tested. These results further support the quenching mechanism is a dynamic process *via* electron transfer.

To determine the limit of detection (LOD) for PL quenching that functionalized Si-NCs display for toluene solutions of NB, MNT, and DNT, the PL quenching arising from analyte concentrations of the range 0.05 - 5 mM was evaluated. The LOD for nitroaromatic compounds in toluene was determined using the 3σ IUPAC criteria and were calculated to be 1.54, 0.995, and 0.341 mM (*i.e.* 184.6, 136.5, and 62.1 ppm, respectively) for NB, MNT, and DNT, respectively.^{16, 17} Unfortunately, solution phase LODs in toluene are not as sensitive as previous reports.²⁸ The origin of the decreased LODs is unclear, however, it may result from the influence of the alkyl surface termination and is the subject of ongoing investigations. Fortunately, these solution LODs do not preclude the practical usefulness of this Si-NCs detection system, which can be extended to solid residue and vapor detection (*vide infra*). Furthermore, it is also reasonable LODs will be improved by appropriate tailoring the surface functional groups.

30 Visual Detection using paper supported Si-NCs

Extending the potential utility of the present Si-NCs sensing motif, we prepared filter paper impregnated with luminescent Si-NCs by dip-coating in a toluene solution of the NCs (Scheme 1).

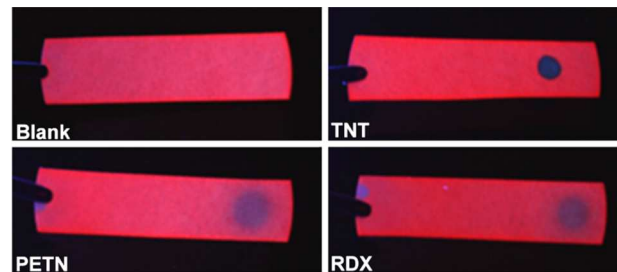


Fig. 2 Images of Si-NCs coated filter paper under a handheld UV-lamp without the presence of nitrocompound and in the presence of solutions of TNT, PETN, and RDX, as indicated.

The resulting paper displayed red-orange photoluminescence characteristic of the Si-NCs upon exposure to a standard handheld UV ($\lambda=365$ nm) lamp (Fig. 2). To test the sensitivity of this new detection system, 2 μ L of stock solutions (0.25, 5, and 25 mM) of NB, MNT, and DNT were spotted onto the prepared paper (Scheme 1). Photographs of the exposed papers are shown in Fig. S3†.

All concentrations tested resulted in complete quenching of the area spotted for every compound. The results indicate the filter paper is more effective at 0.25 and 5 mM concentration than solution phase measurement by the fluorometer where complete quenching at these concentrations was not achieved. There was no visible difference in the quenched spots for all concentrations of NB and MNT. However, DNT displayed a dramatic quenching increase in the area surrounding the initial spot of the compound. As seen in solution, DNT is the most effective of the nitroaromatics tested. To further test the application of the filter paper, 25 μ L of 0.01 mM solutions of explosives TNT, RDX, and PETN were spotted onto the filter paper, and the fluorescence was rapidly and completely quenched for all compounds (Fig. 2). This study showed the filter paper is not only sensitive to nitroaromatics, but also to nitroamines and nitrate esters, and points to the scope of such this sensor motif in real-world applications.

This same filter paper detector can also be applied in the detection of chemical residues. Placing known quantities of DNT residues (*i.e.*, 4.5, 18.2, 91.1 ng) on cotton swabs and exposing the filter paper to the residue (Experimental section in ESI†) indicated the present system can detect as little as 18 ng of DNT (Fig. 3A).

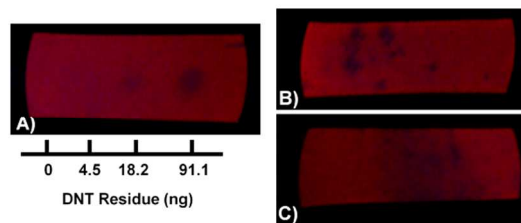


Fig. 3 Solid DNT residue testing onto Si-NCs filter paper by (A) cotton swab tips having different amounts of DNT, DNT residue left after visibly brushing off 0.5 mg DNT from a (B) plastic tray and a (C) cotton fabric, respectively.

The detection of trace residues of DNT on the surfaces of a plastic tray and cotton fabric were also tested (Experimental section in ESI†). Contact of the exposed surface with the filter detection paper resulted in quenching of the Si-NC luminescence (Fig. 3B-C). Further testing was carried out by wiping a gloved finger that had been previously exposed to solid DNT (Experimental section in ESI†). Pressing the finger onto the paper successively 4 times resulted in subsequent quenching (Fig. S4†). Although the exact quantity of DNT residue on the glove decreased with successive printing, the qualitative signal to noise ratio between the first and last print appears to remain unchanged.²⁹ Solid TNT was similarly tested using the glove method, where the contaminated finger was placed on the luminescent area of the detector paper; the luminescence was quenched where the finger was placed (Fig 4). Of important note, control tests (not shown) with a gloved finger, an ungloved finger, and a finger of someone who recently smoked a cigarette provided no quenching.

To further explore the versatility of the present detection system for nitro-compounds in the vapor phase, indicator paper was exposed to the headspace above NB (Experimental section in ESI†). Exposure to NB vapors, completely quenched the Si-NCs within 3 minutes (Fig. S5†) and quenching was reversed upon exposure to a stream of flowing N₂. These results are similar to those reported by Content and coworkers previous report using hydride terminated porous silicon,¹ and confirm the present paper motif offers detection of nitroaromatics in solution as well as vapor and solid phases. The paper-based system may be best adapted as a reliable frontline screening method for on-site detection where rapid detection of explosives and related compounds could prove useful in areas such as landmines, airport and border security etc.¹⁸

Conclusions

In conclusion, the present study demonstrates that luminescent dodecyl functionalized Si-NCs are quenched in the presence of nitroaromatic, nitroamine, and nitrate ester explosive compounds. When tested in solution, the fluorescence intensity decreased with increasing amount of nitroaromatic introduced. The applicability of these Si-NCs was tested by coating them onto a filter paper to generate a luminescent paper-sensor. The paper-sensor successfully detects solution, solid and vapor phase nitroaromatic compounds through visualization of fluorescent quenching under a handheld UV lamp. The versatility was further expanded to the sensing of nitroamines and nitrate esters (*i.e.*, RDX and PETN). The method described here offers a non-toxic, portable, rapid, and straightforward sensing system for on-site detection of nitro group containing explosives. Further testing and development using different surface functional groups other than dodecene could be used to increase sensitivity and selectivity towards nitroaromatic, nitroamine and nitrate ester explosives or for the detection of other molecules.

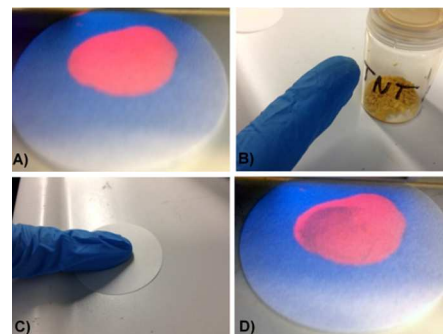


Fig. 4 Images of (A) a spotted filter paper with Si-NCs, (B) a gloved finger with trace amounts of solid TNT, (C) application of solid TNT to the coated filter paper, and (D) observed quenching of luminescent filter paper after contact with solid TNT residue.

Acknowledgements

The authors acknowledge funding from the Natural Sciences and Engineering Research Council of Canada (NSERC), Canada Foundation for Innovation (CFI), Alberta Science and Research Investment Program (ASRIP), Alberta Innovates Technology Futures (AITF), and University of Alberta Department of Chemistry. We would like to thank W. C. Moffat, M. Skjel, and M. Hoyle for assistance with material characterization. Killam trusts, NSERC and Alberta Innovates (AI) are thanked for studentship to MD. Financial support of this work by the Ludwig-Maximilian University of Munich (LMU), the U.S. Army Research Laboratory (ARL) under grant no. W911NF-09-2-0018, the Armament Research, Development and Engineering Center (ARDEC) under grant no. W911NF-12-1-0467, and the Office of Naval Research (ONR) under grant nos. ONR.N00014-10-1-0535 and ONR.N00014-12-1-0538 is gratefully acknowledged. Dr. Al Meldrum is thanked for use of laser facilities for lifetime measurements. All Veinot Team members and Dr. Farooq Wahab are also thanked for useful discussion.

Notes and references

- 1 S. Content, W. C. Trogler, M. J. Sailor, *Chem. Eur. J.* 2000, **6**, 2205.
- 2 I. N. Germanenko, S. Li, M. S. El-Shall, *J. Phys. Chem. B* 2001, **105**, 59.
- 3 K. Zhang, H. Zhou, Q. Mei, S. Wang, G. Guan, R. Liu, J. Zhang, *Z. Zhang, J. Am. Chem. Soc.* 2011, **133**, 8424.
- 4 Y. Ma, H. Li, S. Peng, L. Wang, *Anal. Chem.* 2012, **84**, 8415-8421.
- 5 R. Freeman, T. Finder, L. Bahshi, R. Gill, I. Willner, *Adv. Mater.* 2012, **24**, 6416.
- 6 B. Balan, C. Vijayakumar, M. Tsuji, A. Saeki, S. Seki, *J. Phys. Chem. B* 2012, **116**, 10371.
- 7 M. E. Germain, M. J. Knapp, *Chem. Soc. Rev.* 2009, **38**, 2543-2555.
- 8 Y. Yang, H. Wang, K. Su, Y. Long, Z. Peng, N. Li, F. Liu, *J. Mater. Chem.* 2011, **21**, 11895.
- 9 Y. Salinas, R. Martinez-Manez, M. D. Marcos, F. Sancenon, A. N. Costero, M. Parraad, S. S. Gil, *Chem. Soc. Rev.* 2012, **41**, 1261.
- 10 K. Hakansson, R. V. Coorey, R. A. Zubarev, V. L. Talrose, P. Hakansson, *J. Mass Spectrom.* 2000, **35**, 337.
- 11 M. Najarro, M. E. D. Morris, M. E. Staymates, R. Fletcher, G. Gillen, *Analyst* 2012, **137**, 2614.
- 12 J. M. Sylvia, J. A. Janni, J. D. Klein, K. M. Spencer, *Anal. Chem.* 2000, **72**, 5834.
- 13 R. D. Luggar, M. J. Farquharson, J. A. Horrocks, R. J. Lacey, *J. X-Ray Spectrom.* 1998, **27**, 87.
- 14 J. Feng, Y. Li, M. Yang, *Sensor Actuat. B* 2010, **145**, 438.
- 15 R. Tu, B. Liu, Z. Wang, D. Gao, F. Wang, Q. Fang, Z. Zhang, *Anal. Chem.* 2008, **80**, 3458.

- 16 W. J. Jin, M. T. Fernandez-Arguelles, J. M. Costa-Fernandez, R. Pereiro, R. Sanz-Medel, *Chem. Commun.* 2005, **7**, 883.
- 17 W. J. Jin, J. M. Costa-Fernandez, R. Pereiro, A. Sanz-Medel, *Anal. Chim. Acta* 2004, **522**, 1.
- 5 18 G. H. Shi, Z. B. Shang, Y. Wang, W. J. Jin, T. C. Zhang, *Spectrochim. Acta A* 2008, **70**, 247.
- 19 C. M. Hessel, E. J. Henderson, J. G. C. Veinot, *Chem. Mater.* 2006, **18**, 6139.
- 20 J. A. Kelly, J. G. C. Veinot, *ACS Nano*, 2010, **4**, 4645.
- 10 21 A. M. Derfus, W. C. W. Chan, S. N. Bhatia, *Nano Lett.* 2004, **4**, 11.
- 22 J. M. Rehm, G. L. McLendon, P. M. Fauchet, *J. Am. Chem. Soc.* 1996, **118**, 4490.
- 23 J. C. Scaiano, M. Laferrière, R. E. Galian, V. Maurel, P. Billone, *P. Phys. Stat. Sol. A* 2006, **203**, 1337.
- 15 24 J. M. Costa-Fernandez, R. Pereiro, A. Sanz-Medel, *Trends Anal. Chem.* 2006, **25**, 207.
- 25 R. Freeman, I. Wilner, *Chem. Soc. Rev.* 2012, **41**, 4067.
- 26 J. F. Garcia-Reyes, J. D. Harper, G. A. Salazar, N. A. Charipar, Z. Ouyang, R. G. Cooks, *Anal. Chem.* 2011, **83**, 1084.
- 20 27 A. K. Bar, S. Shanmugaraju, K. Chib, P. S. Mukherjee, *Dalton Trans.* 2011, **40**, 2257.
- 28 T. Shiraki, Y. Tsuchiya, S. Shinkai, *Chem. Lett.* 2010, **39**, 156.
- 29 S. J. Toal, J. C. Sanchez, R. E. Dugan, W. C. Trogler, *J. Forensic Sci.* 2007, **52**, 79.
- 25 30 Y. Liu, K. Ogawa, K. S. Schanze, *J. Photochem. Photobio. C*, 2009, **10**, 173.
- 31 P. M. Fierro-Mercado, S. P. Hernandez-Rivera, *Int. J. Spec.* 2013, **2013**, 1.
- 32 S. Z. Nergiz, N. Gandra, M. E. Farrell, L. Tian, P. M. Pellegrino, S. Singamaneni, *J. Mater. Chem. A*, 2013, **1**, 6543.
- 30

A silicon nanocrystal paper based sensor has been developed for the rapid, on-site detection of nitro-group containing explosive compounds.

