


Faraday Discussions

Accepted Manuscript



This manuscript will be presented and discussed at a forthcoming Faraday Discussion meeting. All delegates can contribute to the discussion which will be included in the final volume.

Register now to attend! Full details of all upcoming meetings: <http://rsc.li/fd-upcoming-meetings>

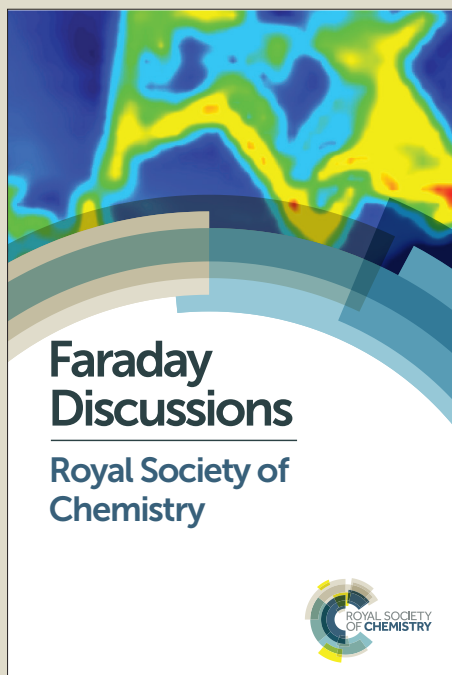

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Mechanochemistry: A versatile synthesis strategy for new materials

William Jones and Mark D. Eddleston

Department of Chemistry
University of Cambridge
Lensfield Road
Cambridge CB2 1EW
UK

Abstract

Mechanochemistry deals with reactions induced by the input of mechanical energy – for example by impacts within a vibratory ball mill. The technique has a long history with significant contributions from Ostwald, Carey Lea and, notably, Faraday. Mechanochemistry has subsequently seen application in a variety of areas of materials science including mechanical alloying in metallurgy, the synthesis of complex organic molecules and, more recently, the discovery and development of new solid forms of active pharmaceutical ingredients. This paper overviews the broad areas of application of mechanochemistry, some key features which make it a particularly attractive approach to materials synthesis and some mechanistic aspects highlighted within the literature. A significant part, however, will focus on recent applications in the area of pharmaceuticals and its important role in exploring the rich variety of solid forms available for small, drug-like, molecules.

1. Introduction

Mechanochemistry is a long-established method for the synthesis of solids and molecules. Its chemical importance was recorded by Faraday, who in 1820 demonstrated the reduction of AgCl to Ag by grinding in a mortar and pestle a mixture of AgCl and Zn. (Takacs, 2007) Significant progress followed, especially through the work of Carey Lea (1823 – 1897), (Takacs, 2003) and the position of mechanochemistry within the framework of chemistry as a whole was established by Ostwald who noted the equivalency of electrochemistry, thermochemistry, photochemistry and mechanochemistry. (Boldyrev, 2006, Baláz, 2008, Takacs, 2013)

Long held as an efficient process for the synthesis of metallic alloys, a recent extensive review by James *et al.* (James *et al.*, 2012) has highlighted several of the emergent areas now being actively pursued with regard to the application of mechanical energy in driving various transformations – indeed a working definition from that review is “mechanochemistry refers to reactions, normally of solids, induced by the impact of mechanical energy such as grinding in ball mills”. A formal definition

by IUPAC states “a mechano-chemical reaction is a chemical reaction that is induced by mechanical energy”.(McNaught and Wilkinson, 1997) Although a narrow definition of mechanochemistry may lead to a suggestion that the making and breaking of covalent bonds would be a prerequisite for a process to fall under the definition of “mechanochemistry”,(Kaupp, 2009) following the appreciation of the importance of “non-covalent bonds” in supramolecular chemistry it seems reasonable to include changes in crystal packing to be a mechanochemical event. Links to mechanochemical activation by ultrasound have also been proposed.(Boldyrev, 1995, Cravotto et al., 2013)

This paper will briefly summarise recent developments in mechanochemistry, particularly in its application in pharmaceutical materials science and its role in the development of new solid drug dosage forms to complement earlier literature which has covered extensively metals and alloys and inorganic (ionic) systems. As we will describe later, the amount of energy which can be imparted to a system under mechanical activation can be significant – certainly sufficient to break chemical bonds(James et al., 2012) – but can also be reduced when working with systems such as soft molecular crystals in order to minimise chemical activation while still enabling processes such as the conversion of a crystalline solid to an amorphous product,(Descamps et al., 2007) or the readjustment of molecules within a lattice. Such readjustments may lead to the introduction of lattice imperfections,(Hüttenrauch et al., 1985) to polymorphic transformations(Li et al., 2007) or to the intimate mixing of two separate crystalline molecular solids to create a crystalline multicomponent product indistinct from that which would be obtained by a conventional solution crystallisation.(Etter et al., 1993) Particularly advantageous in mechanochemical transformations is the avoidance of the need for large volumes of solvent (as required, for example, in the recrystallization of poorly soluble molecules), and hence a strong “Green Chemistry” aspect to mechanochemistry is recognised.(Cave et al., 2001, Cannon and Warner, 2002) In terms of commercial interest, the review by James et al describes a search of patent applications for the terms “mechanochemical” and “mechanochemistry” which revealed a significant increase in usage in the patent literature from 1980 onwards.(James et al., 2012)

2. Areas of application and development.

The areas in which mechanochemistry has been applied with success are varied and include: catalysts,(Ralphs et al., 2013) nanoparticles,(Urakae and Boldyrev, 2005, Smolyakov et al., 2008, Baláž et al., 2013) organic synthesis,(Etter et al., 1989, Mikhailenko et al., 2004, Trotzki et al., 2008, Bruckmann et al., 2008, Štrukil et al., 2012, Stojaković et al., 2012, Wang, 2013) MOFs,(Frišćić, 2012) oxides,(Šepelák et al., 2013) biomaterials,(Hick et al., 2010, Kleine et al., 2013) supramolecular chemistry,(Braga et al., 2006, Belenguer et al., 2011, Delori et al., 2012) process engineering,(Burmeister and Kwade, 2013) dyes and pigments,(Bučar et al., 2013b) fluorophores,(Yan et al., 2011) exfoliation of graphene nanosheets(Shang et al., 2012) and modification of fullerenes (see Figure 1).(Zhu et al., 2013) Numerous further examples are given in the review by James et al(James et al., 2012) and several other reviews on the application of mechanochemistry are available.(Blagden et al., 2008, Baláž and Dutková, 2009, Guo et al., 2009, Black et al., 2011, Boldyreva, 2011, Nasser and Mingelgrin, 2012, Frišćić, 2012, Boldyreva, 2013, Majano et al., 2014) In particular, the contributions of V. V. Boldyrev and his colleagues to both

experimental and theoretical aspects of mechanochemistry have been important to the subject.(Boldyrev, 1995, Boldyrev and Tkáčová, 2000, Boldyrev, 2004, Boldyrev, 2006)

From a synthetic chemistry viewpoint an important observation is that substances can react by a significantly different pathway in the solid state than they would in solution leading to new products or to much higher selectivities.(Toda et al., 1987, Hollingsworth et al., 1991) This ability to generate a much broader product-spectrum, as we will demonstrate later, is also particularly important in areas other than chemical transformations e.g. in crystal polymorph conversions – and it is to be noted that the addition of very small amounts of liquid may have a significant impact on the outcome of a solid-solid reaction, even though quantities are much less than a conventional solvent-based reaction might require – see later.

A key area of active research remains the understanding of the processes by which mechanically induced reactions occur.(Friščić and Jones, 2009) Given the variety of materials of interest, ranging from metals and ceramics to pharmaceuticals, the specific details of how a process occurs will likely be varied and complex.(Boldyrev, 2002, Boldyrev, 2006, Michalchuk et al., 2013) Also to be distinguished is the time-scale over which an event is studied. During the few milliseconds following the impact of two solids at high velocity, significant local consequences will ensue. Hot spots, magma-plasma regions, rapid induction of defects (point, linear and planar) and then propagation of these defects through the crystal are some of the concepts which have evolved. The distribution of imparted energy will also be different in those solids with high rigidity and few pathways for energy dissipation (so that the effects at the specific point of impact will be great) than it is in those systems where structural movement (e.g. slippage of crystal planes) may allow the energy (and its consequences) to be distributed over a much larger distance.(Boldyrev, 2006) During this early stage, the making and breaking of chemical bonds would seem possible. Following the initial short-term consequences, there will also be the longer term events associated with the final energy dissipation and relaxation of the system. The slow crystallisation of an intermediate amorphous phase may be such an example (see Figures 2 and 3).(Shakhtshneider, 1997, Nguyen et al., 2007, Descamps et al., 2007, Friščić and Jones, 2009) It is possible, then, to envisage that an individual particle, for example within a milled pharmaceutical material, may be completely amorphous initially, but over time may change to consist of domains of crystalline solid embedded within an amorphous shell (or more likely *vice versa* where, for example, humidity from the surrounding atmosphere results in each amorphous particle crystallising from the outside). This model might suggest that a description of a product as 25% amorphous does not mean that 25% of all the particles are amorphous and 75% are not – but that each individual particle within the product consists of domains of crystalline and amorphous in a 3:1 ratio.

A key factor for potential commercial exploitation in many instances would seem to be difficulties associated with scale-up. The progression from gram-scale, lab-based synthesis to kilogram-scale or higher outputs is an issue that has been addressed in many industrial applications³ and more recently in the area of pharmaceuticals, where twin extrusion approaches are employed (Figure 4).(Medina et al., 2010, Daurio et al., 2011) Furthermore, it is noteworthy that frequently the generation of a new material (e.g. in the case of molecular crystals) at the gram level can allow, through subsequent seeding of a supersaturated solution, production via a conventional solvent-based crystallisation route.(Trask et al., 2005c)

It is also necessary to recognise the need for methods of structurally characterising the products of mechanochemical processes. When applied to chemical conversions which may occur, molecular identity can be established by conventional analytical methods (e.g. solution NMR and mass spectrometry). For solid-solid transformations, where the identity of crystalline intermediates or final states is required, major improvements in crystal structure determination from powder X-ray diffraction data (frequently coupled with solid-state NMR) has been pivotal.(Cheung et al., 2003, Karki et al., 2007, Salager et al., 2010, Harris, 2012, Arhangelskis et al., 2012) In addition, the structural analysis of individual crystallites that result from mechanochemical processes is possible through utilisation of the electron diffraction facility of the transmission electron microscope.(Kolb et al., 2010, Eddleston et al., 2013b, Eddleston et al., 2013a)

3. Pharmaceutical materials

Within various areas of process engineering (including food science, chemicals and pharmaceuticals) particle size reduction is an important step.(Qiu et al., 2009, Burmeister and Kwade, 2013) Approaches to size reduction include compression (e.g. rollers) or impact (e.g. impact mills and ball mills). All methods involve transfer of varying amounts of energy to the particle(s), and as a result other consequences can accompany the size reduction including the introduction of defects (such as dislocations, point defects and stacking faults)(Hüttenrauch et al., 1985) and in particular amorphisation(Trasi and Byrn, 2012) or polymorphic transformations.(Bruni et al., 2012)

The work of Descamps and others with regard to pharmaceutical materials has clearly demonstrated the critical role of the glass transition temperature, T_g , in determining whether or not a persistent amorphous phase will be generated.(Desprez and Descamps, 2006, Willart et al., 2006, Descamps et al., 2007, Caron et al., 2007) The combination of increased milling intensity and the absence of any plasticisers, which might lower T_g (either as liquid or vapour, e.g. water, from the surrounding atmosphere), will encourage the formation of an amorphous product (Figure 5). The distinction between amorphous and crystalline products is particularly important for pharmaceutical applications given the inherent increased transient solubility (and hence improved bioavailability) associated with amorphous compared to crystalline solid forms.(Hancock and Parks, 2000, Murdande et al., 2010, Newman et al., 2012, Trasi and Byrn, 2012)

Frequently, the amorphisation of a material can be a desirable outcome, especially as a means of increasing the transient solubility of the material or of eliminating compression issues with the crystalline equivalent.(Qiu et al., 2009) This attribute is frequently used in the pharmaceutical industry, and the complex nature of the resulting solids has been extensively studied (especially with regard to the instability of the amorphous form with respect to the crystalline state).(Hancock and Parks, 2000)

Polymorphic transformations from the stable to a metastable form (again with increased apparent solubility) can also be a useful consequence of the application of mechanical energy (Figure 6).(Pudipeddi and Serajuddin, 2005, Lin et al., 2006, Wildfong et al., 2007, Li et al., 2007) Jet-milling, a particle-size reduction method frequently used within the pharmaceutical industry where particle-particle collisions occur within a carrier gas (typically air), has, for example, been found to induce polymorph interconversions along with the size reductions.

With grinding experiments, an approach for directing the polymorphic outcome through addition of a small amount of liquid was described by Trask et al for the cases of anthranilic acid and succinic acid (see Figure 7).(Trask et al., 2005b) For anthranilic acid, interconversion between the three known polymorphic forms occurred depending upon the choice of the added liquid.(Madusanka et al., In Preparation) In the case of succinic acid, while the β -polymorph appeared stable to neat grinding, addition of a few drops of a low polarity liquid (e.g. hexane) caused conversion to the α -polymorph. More polar liquids (e.g. water, acetonitrile or methanol) appeared not to induce the transformation. The actual mechanism of the solid-solid transformation is an area of ongoing interest, especially where the change appears to be crystal-crystal in nature.(Halasz, 2010)

An additional reason for interest in mechanochemical processes comes from the fact that the majority of drugs (80-90%) are formulated as tablets, which are seen as a reliable and general way of delivering medicines, and that the tableting process itself requires the application of significant applied pressures (see Figure 8).(Shakhtshneider, 1997, Brittain, 2002, Boldyreva et al., 2006, Oswald et al., 2009, Moore et al., 2009, Buckner et al., 2010, Mazel et al., 2011, Roopwani and Buckner, 2011, Christensen et al., 2012). Importantly, tablets contain other components (excipients), which are added to enhance performance e.g. lubricants, dissolving agents and so on. When pressure is applied during compression, there is a risk that surface-surface reactions between the components and drug, such as that between dicalcium phosphate dihydrate and aspirin, will lead to enhanced instability.(Cassidy et al., 2012)

More recent interest has focussed on the formation of cocrystals (see Figure 9) by milling or grinding.(Braga and Grepioni, 2004, Trask and Jones, 2005, Braga et al., 2013) One of the earliest examples of a cocrystal obtained by grinding is that of quinhydrone reported in the work of Wohler published in 1844.(Wöhler, 1844) The advantage for this system compared to solution crystallization was shown by Patil et al,(Patil et al., 1984) who demonstrated that simple grinding of mixtures was significantly superior to attempted solution growth, where self oxidation-reduction lowered the efficiency of complex formation. Subsequently, numerous examples of host-complex formation by solid-solid mixing were reported by Toda and co-workers.(Toda et al., 1987) Work by Etter and colleagues also demonstrated how solid-solid grinding could be used to produce hydrogen bonded cocrystals of adenine and thymine derivatives, where a marked selectivity amongst various base pairs was observed.(Etter et al., 1993) Hollingsworth et al(Hollingsworth et al., 1991) used grinding as a means of creating cocrystals of dinitriles and urea, as part of a wide study of inclusion crystals, in cases where solution growth was not possible. Pedireddi et al demonstrated that in some cases a third component is necessary in order for a cocrystallisation reaction to take place(Pedireddi et al., 1996) and Kuroda and her colleagues studied the influence of the addition of a third component on the optical properties of the resulting cocrystals.(Kuroda et al., 2002)

Frequently, the solid state properties of a pure drug can present processing or application problems e.g. particle flow, thermal stability, stability to moisture or ability to be compacted,(Qiu et al., 2009) and, increasingly, poor solubility is an issue.(Blagden et al., 2007, Bethune et al., 2011) The challenge with a badly behaving drug, therefore, is to be able to control the properties of the molecule in the solid state without recourse to chemical modification by covalent chemistry. The use of multicomponent systems, especially *pharmaceutical cocrystals*, and more recently ionic cocrystals,(Braga et al., 2010, Braga et al., 2011b) has been demonstrated to be an effective strategy in such instances.(Almarsson and Zaworotko, 2004, Stahly, 2007, Shan and Zaworotko, 2008,

Meanwell, 2008, Stahly, 2009, Friščić and Jones, 2010, Qiao et al., 2011, Brittain, 2013, Thakuria et al., 2013, Steed, 2013) In terms of property improvement with pharmaceutical cocrystals, various examples are known including: enhancing stability against hydration of an anhydrate form (see Figure 10),(Trask et al., 2005a, Trask et al., 2006, Eddleston et al., 2014b, Eddleston et al., 2014a) developing forms with improved compression properties (for tablet formation)(see Figures 11 and 12),(Sun and Hou, 2008, Karki et al., 2009a) significantly improving the bioavailability of poorly soluble drugs and controlled release strategies e.g. for insulin.(Brader et al., 2002) Trask has reported on the potential intellectual property implications of pharmaceutical cocrystals,(Trask, 2007) and recent interest has also focussed on regulatory guidelines.(Aitipamula et al., 2012) In non-pharmaceutical applications, benefits of cocrystallisation have been shown for fluorescent materials(Yan et al., 2011, Frenette et al., 2013) and explosives.(Landenberger and Matzger, 2010, Shen et al., 2011)

An early indication of the potential to form pharmaceutical cocrystals by grinding was provided by Caira et al in 1995 who used grinding to prepare a series of crystalline products containing sulfonamide (similar to those obtained from solution) in a facile manner.(Caira et al., 1995) They also reported detailed solid state kinetic data based on powder X-ray measurements and were able to show a distinct selectivity between reactants during grinding.

An ongoing challenge, however, is selecting possible cofomers which might cocrystallise with the API rather than remain as a separate and distinct crystalline phase. Whilst various strategies have been developed to predict the likelihood of cocrystal formation,(Fábián, 2009, Musumeci et al., 2011, Springuel et al., 2012, Wood et al., 2014) experimental screening for viable cofomers remains vital (Figure 13).(Andre et al., 2009, Bysouth et al., 2011, Abourahma et al., 2012) While solution growth remains the ideal approach - especially with regard to scale-up in later stages of development - significant differences in solubility between the drug and cofomer often presents difficulties.(Gagnière et al., 2009, Gagnière et al., 2012, Eddleston et al., 2013c, Eddleston et al., 2014b, Eddleston et al., 2014a) Mechanochemistry has emerged as a powerful tool in the experimental screening area, and has the advantage of minimising the need for large volumes of solvent (Figure 14). It has also emerged as a powerful way of searching for different polymorphic forms of cocrystals(Eddleston et al., 2013c, Madusanka et al., 2014) as well as for various stoichiometric compositions e.g. 1:1, 1:2 and 2:1.(Trask et al., 2005c) Furthermore, mechanochemistry has been used to identify chiral agents suitable for converting a racemate into two distinct diastereomeric cocrystal phases(Eddleston et al., 2012) as well as for cofomer exchange.(Braga et al., 2011a)

An extension to simple (i.e. neat or dry) grinding of mixtures was reported by Shan et al who added a few drops of liquid to the reaction mixture (liquid assisted grinding, LAG) (see Figure 15).(Shan et al., 2002) Initial attention focused on LAG as a means of accelerating cocrystallisation kinetics, although it was subsequently shown to provide a means of increasing product diversity. For example, the outcome of mechanochemical formation of cocrystals has been compared with that from using other approaches to cocrystallisation. Trask et al reported three possible outcomes in the case of cocrystals with caffeine: (i) solution growth and milling produced identical products, (ii) a different stoichiometric product could be obtained by milling compared to solution and (iii) different polymorphic forms were possible.(Trask et al., 2005c) Numerous recent publications have demonstrated that LAG is likely to be the most efficient way of screening for cocrystal

formation.(Myz et al., 2009, Aakeröy et al., 2011, Fucke et al., 2012, Yamamoto et al., 2012, Lin et al., 2014) The key advantage of LAG over solution based approaches was interpreted by Davey,(Chiarella et al., 2007, Chadwick et al., 2009) Childs(Childs et al., 2008) and others(Frišćić et al., 2009) on the basis of solution phase chemistry (Figure 16). Other developments, such as ion- and liquid- assisted grinding (ILAG)(Frišćić et al., 2010b) and vapour digestion of solid mixtures,(Braga and Grepioni, 2005, Braga et al., 2007) have also been reported.

Further insight has been given by the recent work of Bučar et al for the case of caffeine and benzoic acid.(Bučar et al., 2013a) No cocrystals for this pair of molecules were known despite a strong expectation based on studies of analogous systems(Heiden et al., 2012) and despite extensive experimental efforts to generate such a species over many years. A systematic study using a large range of cocrystallisation methods including neat grinding, liquid assisted grinding, melt crystallization and various solution methods was employed (Figure 17). All failed to produce the elusive cocrystal even though theoretical work had clearly confirmed a cocrystal was thermodynamically feasible. During grinding experiments, however, the addition of a few seed crystals of an isostructural fluorobenzoic acid cocrystal readily generated the elusive cocrystal, with the inference being that, as in solution crystallisation, a high barrier to nucleation of a particular form can frequently exist.

Accompanying the recent developments in mechanochemistry has been the development of techniques to follow the course of solid-solid reactions using both *ex situ* and *in situ* approaches.(Nguyen et al., 2007, Cinčić et al., 2008, Tumanov et al., 2011, Du et al., 2013, Frenette et al., 2013, Halasz et al., 2013, Frišćić et al., 2013) *Ex situ* analysis has frequently suggested that there may be distinct intermediates generated (Figure 18).(Cinčić et al., 2008, Karki et al., 2009b) The application of synchrotron X-ray diffraction for *in situ* studies has indeed confirmed the presence of crystalline intermediates and a possible role of amorphous phases.(Halasz et al., 2013) To better understand the processes occurring during milling, several recent efforts have concerned developing methods to follow *in situ* the course of the reaction. Noteworthy has been the use of synchrotron X-ray diffraction. In a study of the milling of a mixture of carbamazepine and succinic acid, Halasz et al(Halasz et al., 2013) showed that, in the absence of any added liquid, the outcome was the gradual disappearance of reflections of the two components and apparent amorphisation. A similar experiment, but now with the addition of 50 μL of acetonitrile showed that within 10 seconds of milling, reflections associated with a triclinic (cbz)(sac) cocrystal emerged. The reaction was complete within 4 minutes. Such rapidity was to be compared with other solid-solid grinding systems (e.g. the reaction of ZnO with imidazoles) where reaction timescales were much longer. Similar *in situ* studies were conducted for suberic acid and nicotinamide demonstrating that formation of a 2:1 cocrystal during grinding proceeds via a 1:1 cocrystal intermediate (see Figure 19). Frišćić and his colleagues have also used *in situ* methods, based on the changes in fluorescence(Frenette et al., 2013) accompanying cocrystallisation, to monitor directly events within the grinding jar.

4. Concluding remarks

In the case of pharmaceutical solids, recent work using atomic force microscopy (AFM), terahertz spectroscopy and transmission electron microscopy (TEM) suggests that these techniques will be

important for characterising mechanically treated samples and understanding changes which occur during such processing. For example, there are particle-particle effects – especially important during compression in a tablet containing various components. In the case of aspirin (acetylsalicylic acid) and dicalcium phosphate, when the excipient was attached to the tip of the AFM cantilever and different pressures and contact times under various humidity conditions there was evidence for enhanced reactivity induced by surface contact with excipient.(Cassidy et al., 2012) Terahertz spectroscopy has emerged as a sensitive method of monitoring changes in solid form during mechanical activation (see Figure 20),(Nguyen et al., 2007, Du et al., 2013) whereas TEM has been shown to be a powerful technique for characterising the size and shape of particulates generated mechanochemically, as well as determining their crystal form (see Figure 21). TEM can also be used to identify defects in pharmaceutical crystals (see Figure 22), and will enable a greater understanding of how defects introduced into crystals during mechanical processing influence material properties, for example a link between defects in theophylline crystals and crystal fracture has been established.(Eddleston et al., 2010)

Mechanochemistry, as mentioned at the outset, provides many opportunities for developing environmentally-friendly processes (especially the avoidance of large volumes of solvent). It also provides routes to materials not readily obtained by other methods. It has a long history and no doubt will continue to demonstrate useful applications whilst at the same time generate considerable activity in rationalising the mechanistic aspects behind the many types of transformations observed.

5. References

- Aakeröy, C. B., Grommet, A. B. and Desper, J. (2011) 'Co-crystal screening of diclofenac', *Pharmaceutics*, 3: 601-614.
- Abourahma, H., Urban, J. M., Morozowich, N. and Chan, B. (2012) 'Examining the robustness of a theophylline cocrystal during grinding with additives', *CrystEngComm*, 14(19): 6163-6169.
- Aitipamula, S., Banerjee, R., Bansal, A. K., Biradha, K., Cheney, M. L., Choudhury, A. R., Desiraju, G. R., Dikundwar, A. G., Dubey, R., Duggirala, N., Ghogale, P. P., Ghosh, S., Goswami, P. K., Goud, N. R., Jetti, R. R. K. R., Karpinski, P., Kaushik, P., Kumar, D., Kumar, V., Moulton, B., Mukherjee, A., Mukherjee, G., Myerson, A. S., Puri, V., Ramanan, A., Rajamannar, T., Reddy, C. M., Rodríguez-Hornedo, N., Rogers, R. D., Row, T. N. G., Sanphui, P., Shan, N., Shete, G., Singh, A., Sun, C. C., Swift, J. A., Thaimattam, R., Thakur, T. S., Kumar Thaper, R., Thomas, S. P., Tothadi, S., Vangala, V. R., Variankaval, N., Vishweshwar, P., Weyna, D. R. and Zaworotko, M. J. (2012) 'Polymorphs, salts, and cocrystals: What's in a name?', *Cryst. Growth Des.*, 12(5): 2147-2152.
- Almarsson, O. and Zaworotko, M. J. (2004) 'Crystal engineering of the composition of pharmaceutical phases. Do pharmaceutical co-crystals represent a new path to improved medicines?', *Chem. Commun.*, (17): 1889-1896.

- Andre, V., Braga, D., Grepioni, F. and Duarte, M. T. (2009) 'Crystal Forms of the Antibiotic 4-Aminosalicylic Acid: Solvates and Molecular Salts with Dioxane, Morpholine, and Piperazine', *Cryst. Growth Des.*, 9(12): 5108-5116.
- Arhangelskis, M., Lloyd, G. O. and Jones, W. (2012) 'Mechanochemical synthesis of pyrazine:dicarboxylic acid cocrystals and a study of dissociation by quantitative phase analysis', *CrystEngComm*, 14(16): 5203-5208.
- Baláž, P. (2008) *Mechanochemistry in Nanoscience and Minerals Engineering*, Berlin, Germany: Springer-Verlag.
- Baláž, P., Achimovičová, M., Baláž, M., Billik, P., Cherkezova-Zheleva, Z., Criado, J. M., Delogu, F., Dutková, E., Gaffet, E., Gotor, F. J., Kumar, R., Mitov, I., Rojac, T., Senna, M., Streletskii, A. and Wiczorek-Ciurawa, K. (2013) 'Hallmarks of mechanochemistry: from nanoparticles to technology', *Chem. Soc. Rev.*, 42(18): 7571-7637.
- Baláž, P. and Dutková, E. (2009) 'Fine milling in applied mechanochemistry', *Miner. Eng.*, 22(7-8): 681-694.
- Belenguer, A. M., Friščić, T., Day, G. M. and Sanders, J. K. M. (2011) 'Solid-state dynamic combinatorial chemistry: reversibility and thermodynamic product selection in covalent mechanosynthesis', *Chem. Sci.*, 2(4): 696-700.
- Bethune, S. J., Schultheiss, N. and Henck, J.-O. (2011) 'Improving the Poor Aqueous Solubility of Nutraceutical Compound Pterostilbene through Cocrystal Formation', *Cryst. Growth Des.*, 11(7): 2817-2823.
- Black, A. L., Lenhardt, J. M. and Craig, S. L. (2011) 'From molecular mechanochemistry to stress-responsive materials', *J. Mater. Chem.*, 21(6): 1655-1663.
- Blagden, N., Berry, D. J., Parkin, A., Javed, H., Ibrahim, A., Gavan, P. T., De Matos, L. L. and Seaton, C. C. (2008) 'Current directions in co-crystal growth', *New Journal of Chemistry*, 32(10): 1659-1672.
- Blagden, N., de Matos, M., Gavan, P. T. and York, P. (2007) 'Crystal engineering of active pharmaceutical ingredients to improve solubility and dissolution rates', *Adv. Drug Delivery Rev.*, 59(7): 617-630.
- Boldyrev, V. V. (1995) 'Mechanochemistry and sonochemistry', *Ultrason. Sonochem.*, 2(2): S143-S145.
- Boldyrev, V. V. (2002) 'Hydrothermal reactions under mechanochemical action', *Powder Technol.*, 122(2-3): 247-254.
- Boldyrev, V. V. (2004) 'Mechanochemical modification and synthesis of drugs', *J. Mater. Sci.*, 39(16-17): 5117-5120.
- Boldyrev, V. V. (2006) 'Mechanochemistry and mechanical activation of solids', *Russ. Chem. Rev.*, 75(3): 177-189.
- Boldyrev, V. V. and Tkáčová, K. (2000) 'Mechanochemistry of solids: past, present, and prospects', *J. Mater. Synth. Process.*, 8(3/4): 121-132.
- Boldyreva, E. (2013) 'Mechanochemistry of inorganic and organic systems: what is similar, what is different?', *Chem. Soc. Rev.*, 42(18): 7719-7738.
- Boldyreva, E. V. (2011) 'Mechanochemistry of organic solids: where are we now?', paper presented at the VI International Conference on Mechanochemistry and Mechanical Alloying (INCOME 2008), NML Jamshedpur, India.
- Boldyreva, E. V., Dmitriev, V. and Hancock, B. C. (2006) 'Effect of pressure up to 5.5GPa on dry powder samples of chlorpropamide form-A', *Int. J. Pharm.*, 327(1-2): 51-57.
- Brader, M. L., Sukumar, M., Pekar, A. H., McClellan, D. S., Chance, R. E., Flora, D. B., Cox, A. L., Irwin, L. and Myers, S. R. (2002) 'Hybrid insulin cocrystals for controlled release delivery', *Nat. Biotechnol.*, 20(8): 800-804.
- Braga, D., D'Addario, D., Maini, L., Polito, M., Giuffreda, S., Rubini, K. and Grepioni, F. (2006) 'Applications of Crystal Engineering Strategies in Solvent-free Reactions: Toward a

- Supramolecular Green Chemistry', in Tiekink, E. R. T. and Vittal, J. J. (eds) *Frontiers in Crystal Engineering*. Chichester, UK, John Wiley & Sons, Ltd.
- Braga, D., Giuffreda, S. L., Grepioni, F., Chierotti, M. R., Gobetto, R., Palladino, G. and Polito, M. (2007) 'Solvent effect in a "solvent free" reaction', *CrystEngComm*, 9(10): 879-881.
- Braga, D. and Grepioni, F. (2004) 'Solventless reactions: Reactions between or within molecular crystals', *Angew. Chem., Int. Ed.*, 43(31): 4002-4011.
- Braga, D. and Grepioni, F. (2005) 'Making crystals from crystals: a green route to crystal engineering and polymorphism', *Chem. Commun.*, (29): 3635-3645.
- Braga, D., Grepioni, F. and Lampronti, G. I. (2011a) 'Supramolecular metathesis: co-former exchange in co-crystals of pyrazine with (R,R)-, (S,S)-, (R,S)- and (S,S/R,R)-tartaric acid', *CrystEngComm*, 13(9): 3122-3124.
- Braga, D., Grepioni, F., Lampronti, G. I., Maini, L. and Turrina, A. (2011b) 'Ionic Co-crystals of Organic Molecules with Metal Halides: A New Prospect in the Solid Formulation of Active Pharmaceutical Ingredients', *Cryst. Growth Des.*, 11(12): 5621-5627.
- Braga, D., Grepioni, F., Maini, L., Prosperi, S., Gobetto, R. and Chierotti, M. R. (2010) 'From unexpected reactions to a new family of ionic co-crystals: the case of barbituric acid with alkali bromides and cesium iodide', *Chem. Commun.*, 46(41): 7715-7717.
- Braga, D., Maini, L. and Grepioni, F. (2013) 'Mechanochemical preparation of co-crystals', *Chem. Soc. Rev.*, 42(18): 7638-7648.
- Brittain, H. G. (2002) 'Effects of mechanical processing on phase composition', *J. Pharm. Sci.*, 91(7): 1573-1580.
- Brittain, H. G. (2013) 'Pharmaceutical cocrystals: The coming wave of new drug substances', *J. Pharm. Sci.*, 102(2): 311-317.
- Bruckmann, A., Krebs, A. and Bolm, C. (2008) 'Organocatalytic reactions. Effects of ball milling, microwave and ultrasound irradiation', *Green Chem.*, 10(11): 1131-1141.
- Bruni, G., Berbenni, V., Sartor, F., Milanese, C., Girella, A., Franchi, D. and Marini, A. (2012) 'Quantification methods of amorphous/crystalline fractions in high-energy ball milled pharmaceutical products', *J. Therm. Anal. Calorim.*, 108(1): 235-241.
- Buckner, I. S., Friedman, R. A. and Wurster, D. E. (2010) 'Using compression calorimetry to characterize powder compaction behavior of pharmaceutical materials', *J. Pharm. Sci.*, 99(2): 861-870.
- Burmeister, C. F. and Kwade, A. (2013) 'Process engineering with planetary ball mills', *Chem. Soc. Rev.*, 42(18): 7660-7667.
- Bučar, D.-K., Day, G. M., Halasz, I., Zhang, G. G. Z., Sander, J. R. G., Reid, D. G., MacGillivray, L. R., Duer, M. J. and Jones, W. (2013a) 'The curious case of (caffeine)-(benzoic acid): how heteronuclear seeding allowed the formation of an elusive cocrystal', *Chem. Sci.*, 4(12): 4417-4425.
- Bučar, D.-K., Filip, S., Arhangel'skis, M., Lloyd, G. O. and Jones, W. (2013b) 'Advantages of mechanochemical cocrystallisation in the solid-state chemistry of pigments: colour-tuned fluorescein cocrystals', *CrystEngComm*, 15(32): 6289-6291.
- Bysouth, S. R., Bis, J. A. and Igo, D. (2011) 'Cocrystallization via planetary milling: Enhancing throughput of solid-state screening methods', *Int. J. Pharm.*, 411(1-2): 169-171.
- Caira, M. R., Nassimbeni, L. R. and Wildervanck, A. F. (1995) 'Selective formation of hydrogen bonded cocrystals between a sulfonamide and aromatic carboxylic acids in the solid state', *Journal of the Chemical Society, Perkin Transactions 2: Physical Organic Chemistry*, (12): 2213-16.
- Cannon, A. S. and Warner, J. C. (2002) 'Noncovalent derivatization: green chemistry applications of crystal engineering', *Cryst. Growth Des.*, 2(4): 255-257.
- Caron, V., Willart, J. F., Danede, F. and Descamps, M. (2007) 'The implication of the glass transition in the formation of trehalose/mannitol molecular alloys by ball milling', *Solid State Commun.*, 144(7-8): 288-292.

- Cassidy, A. M., Gardner, C. E., Auffret, T., Aldous, B. and Jones, W. (2012) 'Decoupling the effects of surface chemistry and humidity on solid-state hydrolysis of aspirin in the presence of dicalcium phosphate dihydrate', *J. Pharm. Sci.*, 101(4): 1496-1507.
- Cave, G. W. V., Raston, C. L. and Scott, J. L. (2001) 'Recent advances in solventless organic reactions: towards benign synthesis with remarkable versatility', *Chem. Commun.*, (21): 2159-2169.
- Chadwick, K., Davey, R., Sadiq, G., Cross, W. and Pritchard, R. (2009) 'The utility of a ternary phase diagram in the discovery of new co-crystal forms', *CrystEngComm*, 11(3): 412-414.
- Cheung, E. Y., Kitchin, S. J., Harris, K. D. M., Imai, Y., Tajima, N. and Kuroda, R. (2003) 'Direct Structure Determination of a Multicomponent Molecular Crystal Prepared by a Solid-State Grinding Procedure', *J. Am. Chem. Soc.*, 125(48): 14658-14659.
- Chiarella, R. A., Davey, R. J. and Peterson, M. L. (2007) 'Making co-crystals - The utility of ternary phase diagrams', *Cryst. Growth Des.*, 7(7): 1223-1226.
- Childs, S. L., Rodríguez-Hornedo, N., Reddy, L. S., Jayasankar, A., Maheshwari, C., McCausland, L., Shipplett, R. and Stahly, B. C. (2008) 'Screening strategies based on solubility and solution composition generate pharmaceutically acceptable cocrystals of carbamazepine', *CrystEngComm*, 10(7): 856-864.
- Christensen, N. P. A., Cornett, C. and Rantanen, J. (2012) 'Role of excipients on solid-state properties of piroxicam during processing', *J. Pharm. Sci.*, 101(3): 1202-1211.
- Cinčić, D., Friščić, T. and Jones, W. (2008) 'A Stepwise Mechanism for the Mechanochemical Synthesis of Halogen-Bonded Cocrystal Architectures', *J. Am. Chem. Soc.*, 130(24): 7524-7525.
- Cravotto, G., Gaudino, E. C. and Cintas, P. (2013) 'On the mechanochemical activation by ultrasound', *Chem. Soc. Rev.*, 42(18): 7521-7534.
- Daurio, D., Medina, C., Saw, R., Nagapudi, K. and Alvarez-Nunez, F. (2011) 'Application of twin screw extrusion in the manufacture of cocrystals, part I: four case studies', *Pharmaceutics*, 3: 582-600.
- Delori, A., Friščić, T. and Jones, W. (2012) 'The role of mechanochemistry and supramolecular design in the development of pharmaceutical materials', *CrystEngComm*, 14(7): 2350-2362.
- Descamps, M., Willart, J. F., Dudognon, E. and Caron, V. (2007) 'Transformation of pharmaceutical compounds upon milling and comilling: The role of T-g', *Journal of Pharmaceutical Sciences*, 96(5): 1398-1407.
- Desprez, S. and Descamps, M. (2006) 'Transformations of glassy indomethacin induced by ball-milling', *J. Non-Cryst. Solids FIELD Full Journal Title: Journal of Non-Crystalline Solids*, 352(42-49): 4480-4485.
- Du, Y., Xia, Y., Zhang, H. and Hong, Z. (2013) 'Using terahertz time-domain spectroscopical technique to monitor cocrystal formation between piracetam and 2,5-dihydroxybenzoic acid', *Spectrochim. Acta, Part A*, 111: 192-195.
- Eddleston, M. D., Arhangelskis, M., Friščić, T. and Jones, W. (2012) 'Solid state grinding as a tool to aid enantiomeric resolution by cocrystallisation', *Chem. Commun.*, 48(92): 11340-11342.
- Eddleston, M. D., Bithell, E. G. and Jones, W. (2010) 'Transmission electron microscopy of pharmaceutical materials', *Journal of Pharmaceutical Sciences*, 99(9): 4072-4083.
- Eddleston, M. D., Hejczyk, K. E., Bithell, E. G., Day, G. M. and Jones, W. (2013a) 'Determination of the crystal structure of a new polymorph of theophylline', *Chem. - Eur. J.*, 19(24): 7883-7888.
- Eddleston, M. D., Hejczyk, K. E., Bithell, E. G., Day, G. M. and Jones, W. (2013b) 'Polymorph identification and crystal structure determination by a combined crystal structure prediction and transmission electron microscopy approach', *Chem. - Eur. J.*, 19(24): 7874-7882.
- Eddleston, M. D., Madusanka, N. and Jones, W. (2014a) 'Cocrystal Dissociation in the Presence of Water: A General Approach for Identifying Stable Cocrystal Forms', *J. Pharm. Sci.*: Ahead of Print. DOI: 10.1002/jps.24003.
- Eddleston, M. D., Sivachelvam, S. and Jones, W. (2013c) 'Screening for polymorphs of cocrystals: a case study', *CrystEngComm*, 15(1): 175-181.

- Eddleston, M. D., Thakuria, R., Aldous, B. J. and Jones, W. (2014b) 'An Investigation of the Causes of Cocrystal Dissociation at High Humidity', *J. Pharm. Sci.*: Ahead of Print.
DOI: 10.1002/jps.23865.
- Etter, M. C., Frankenbach, G. M. and Bernstein, J. (1989) 'Solid-state nucleophilic aromatic substitution reaction of a carboxylic acid cocrystal', *Tetrahedron Lett.*, 30(28): 3617-20.
- Etter, M. C., Reutzel, S. M. and Choo, C. G. (1993) 'Self-organization of adenine and thymine in the solid state', *J. Am. Chem. Soc.*, 115(10): 4411-12.
- Frenette, M., Cosa, G. and Friščić, T. (2013) 'Characterisation of organic solid forms and real-time in situ monitoring of their transformations using solid-state fluorescence', *CrystEngComm*, 15(25): 5100-5106.
- Friščić, T. (2012) 'Supramolecular concepts and new techniques in mechanochemistry: cocrystals, cages, rotaxanes, open metal-organic frameworks', *Chem. Soc. Rev.*, 41(9): 3493-3510.
- Friščić, T., Childs, S. L., Rizvi, S. A. A. and Jones, W. (2009) 'The role of solvent in mechanochemical and sonochemical cocrystal formation: a solubility-based approach for predicting cocrystallisation outcome', *CrystEngComm*, 11(3): 418-426.
- Friščić, T., Halasz, I., Beldon, P. J., Belenguer, A. M., Adams, F., Kimber, S. A. J., Honkimäki, V. and Dinnebier, R. E. (2013) 'Real-time and in situ monitoring of mechanochemical milling reactions', *Nat. Chem.*, 5(1): 66-73.
- Friščić, T. and Jones, W. (2009) 'Recent Advances in Understanding the Mechanism of Cocrystal Formation via Grinding', *Crystal Growth & Design*, 9(3): 1621-1637.
- Friščić, T. and Jones, W. (2010) 'Benefits of cocrystallization in pharmaceutical materials science: an update', *J. Pharm. Pharmacol.*, 62(11): 1547-1559.
- Friščić, T., Lancaster, R. W., Fábrián, L. and Karamertzanis, P. G. (2010a) 'Tunable recognition of the steroid α -face by adjacent π -electron density', *Proc. Natl. Acad. Sci. U. S. A.*, 107(30): 13216-13221.
- Friščić, T., Reid, D. G., Halasz, I., Stein, R. S., Dinnebier, R. E. and Duer, M. J. (2010b) 'Ion- and Liquid-Assisted Grinding: Improved Mechanochemical Synthesis of Metal-Organic Frameworks Reveals Salt Inclusion and Anion Templating', *Angew. Chem., Int. Ed.*, 49(4): 712-715, S712/1-S712/17.
- Fucke, K., Myz, S. A., Shakhthshneider, T. P., Boldyreva, E. V. and Griesser, U. J. (2012) 'How good are the crystallisation methods for co-crystals? A comparative study of piroxicam', *New J. Chem.*, 36(10): 1969-1977.
- Fábrián, L. (2009) 'Cambridge Structural Database Analysis of Molecular Complementarity in Cocrystals', *Crystal Growth & Design*, 9(3): 1436-1443.
- Gagnière, E., Mangin, D., Puel, F., Rivoire, A., Monnier, O., Garcia, E. and Klein, J. P. (2009) 'Formation of co-crystals: Kinetic and thermodynamic aspects', *J. Cryst. Growth*, 311(9): 2689-2695.
- Gagnière, E., Mangin, D., Veessler, S. and Puel, F. (2012) 'Co-crystallization in solution and scale-up issues', *RSC Drug Discovery Ser.*, 16(Pharmaceutical Salts and Co-crystals): 188-211.
- Guo, X., Xiang, D., Duan, G. and Mou, P. (2009) 'A review of mechanochemistry applications in waste management', *Waste Manage.*, 30(1): 4-10.
- Halasz, I. (2010) 'Single-Crystal-to-Single-Crystal Reactivity: Gray, Rather than Black or White', *Cryst. Growth Des.*, 10(7): 2817-2823.
- Halasz, I., Puškarić, A., Kimber, S. A. J., Beldon, P. J., Belenguer, A. M., Adams, F., Honkimäki, V., Dinnebier, R. E., Patel, B., Jones, W., Štrukil, V. and Friščić, T. (2013) 'Real-Time In Situ Powder X-ray Diffraction Monitoring of Mechanochemical Synthesis of Pharmaceutical Cocrystals', *Angew. Chem., Int. Ed.*, 52(44): 11538-11541.
- Hancock, B. C. and Parks, M. (2000) 'What is the true solubility advantage for amorphous pharmaceuticals?', *Pharm. Res.*, 17(4): 397-404.
- Harris, K. D. M. (2012) 'Powder diffraction crystallography of molecular solids', *Top. Curr. Chem.*, 315(Advanced X-Ray Crystallography): 133-178.

- Heiden, S., Troebels, L., Wenzel, K.-J. and Emmerling, F. (2012) 'Mechanochemical synthesis and structural characterisation of a theophylline-benzoic acid cocrystal (1 : 1)', *CrystEngComm*, 14(16): 5128-5129.
- Hick, S. M., Griebel, C., Restrepo, D. T., Truitt, J. H., Buker, E. J., Bylda, C. and Blair, R. G. (2010) 'Mechanocatalysis for biomass-derived chemicals and fuels', *Green Chem.*, 12(3): 468-474.
- Hollingsworth, M. D., Santarsiero, B. D., Oumar-Mahamat, H. and Nichols, C. J. (1991) 'New series of 1:1 layered complexes of α,ω -dinitriles and urea', *Chem. Mater.*, 3(1): 23-5.
- Hüttenrauch, R., Fricke, S. and Zielke, P. (1985) 'Mechanical activation of pharmaceutical systems', *Pharm. Res.*, (6): 302-6.
- James, S. L., Adams, C. J., Bolm, C., Braga, D., Collier, P., Friščić, T., Grepioni, F., Harris, K. D. M., Hyett, G., Jones, W., Krebs, A., Mack, J., Maini, L., Orpen, A. G., Parkin, I. P., Shearouse, W. C., Steed, J. W. and Waddell, D. C. (2012) 'Mechanochemistry: opportunities for new and cleaner synthesis', *Chem. Soc. Rev.*, 41(1): 413-447.
- Karki, S., Friščić, T., Fábíán, L., Laity, P. R., Day, G. M. and Jones, W. (2009a) 'Improving mechanical properties of crystalline solids by cocrystal formation: new compressible forms of paracetamol', *Adv. Mater.*, 21(38-39): 3905-3909.
- Karki, S., Friščić, T. and Jones, W. (2009b) 'Control and interconversion of cocrystal stoichiometry in grinding: stepwise mechanism for the formation of a hydrogen-bonded cocrystal', *CrystEngComm*, 11(3): 470-481.
- Karki, S., Fábíán, L., Friščić, T. and Jones, W. (2007) 'Powder x-ray diffraction as an emerging method to structurally characterize organic solids', *Organic Letters*, 9(16): 3133-3136.
- Kaupp, G. (2009) 'Mechanochemistry: the varied applications of mechanical bond-breaking', *CrystEngComm*, 11(3): 388-403.
- Kleine, T., Buendia, J. and Bolm, C. (2013) 'Mechanochemical degradation of lignin and wood by solvent-free grinding in a reactive medium', *Green Chem.*, 15(1): 160-166.
- Kolb, U., Gorelik, T. E., Mugnaioli, E. and Stewart, A. (2010) 'Structural Characterization of Organics Using Manual and Automated Electron Diffraction', *Polymer Reviews*, 50(3): 385-409.
- Kuroda, R., Imai, Y. and Tajima, N. (2002) 'Generation of a co-crystal phase with novel coloristic properties via solid state grinding procedures', *Chem. Commun.*, (23): 2848-2849.
- Landenberger, K. B. and Matzger, A. J. (2010) 'Cocrystal Engineering of a Prototype Energetic Material: Supramolecular Chemistry of 2,4,6-Trinitrotoluene', *Cryst. Growth Des.*, 10(12): 5341-5347.
- Li, H., Stowell, J. G., He, X., Morris, K. R. and Byrn, S. R. (2007) 'Investigations on solid-solid phase transformation of 5-methyl-2-[(4-methyl-2-nitrophenyl)amino]-3-thiophenecarbonitrile', *J. Pharm. Sci.*, 96(5): 1079-1089.
- Lin, H.-L., Wu, T.-K. and Lin, S.-Y. (2014) 'Screening and characterization of cocrystal formation of metaxalone with short-chain dicarboxylic acids induced by solvent-assisted grinding approach', *Thermochim. Acta*, 575: 313-321.
- Lin, S.-Y., Cheng, W.-T. and Wang, S.-L. (2006) 'Thermodynamic and kinetic characterization of polymorphic transformation of famotidine during grinding', *Int. J. Pharm.*, 318(1-2): 86-91.
- Madusanka, N., Eddleston, M. D., Arhangelskis, M. and Jones, W. (2014) 'Polymorphs, hydrates and solvates of a co-crystal of caffeine with anthranilic acid', *Acta Crystallogr., Sect. B Struct. Sci., Cryst. Eng. Mater.*, 70(1): 72-80.
- Madusanka, N., Eddleston, M. D. and Jones, W. (In Preparation).
- Majano, G., Borchardt, L., Mitchell, S., Valtchev, V. and Perez-Ramirez, J. (2014) 'Rediscovering zeolite mechanochemistry - A pathway beyond current synthesis and modification boundaries', *Microporous Mesoporous Mater.*, 194: 106-114.
- Mazel, V., Delplace, C., Busignies, V., Faivre, V., Tchoreloff, P. and Yagoubi, N. (2011) 'Polymorphic transformation of anhydrous caffeine under compression and grinding: a re-evaluation', *Drug Dev. Ind. Pharm.*, 37(7): 832-840.

- McNaught, A. D. and Wilkinson, A. (1997) *IUPAC. Compendium of Chemical Terminology*, Oxford: Blackwell Scientific Publications.
- Meanwell, N. A. (2008) 'The emerging utility of co-crystals in drug discovery and development', *Annu. Rep. Med. Chem.*, 43: 373-404.
- Medina, C., Daurio, D., Nagapudi, K. and Alvarez-Nunez, F. (2010) 'Manufacture of pharmaceutical co-crystals using twin screw extrusion: a solvent-less and scalable process', *J. Pharm. Sci.*, 99(4): 1693-1696.
- Michalchuk, A. A. L., Tumanov, I. A. and Boldyreva, E. V. (2013) 'Complexities of mechanochemistry: elucidation of processes occurring in mechanical activators via implementation of a simple organic system', *CrystEngComm*, 15(32): 6403-6412.
- Mikhailenko, M. A., Shakhtshneider, T. P. and Boldyrev, V. V. (2004) 'On the mechanism of mechanochemical synthesis of phthalylsulphathiazole', *J. Mater. Sci.*, 39(16-17): 5435-5439.
- Moore, M. D., Steinbach, A. M., Buckner, I. S. and Wildfong, P. L. D. (2009) 'A Structural Investigation into the Compaction Behavior of Pharmaceutical Composites Using Powder X-ray Diffraction and Total Scattering Analysis', *Pharm. Res.*, 26(11): 2429-2437.
- Murdande, S. B., Pikal, M. J., Shanker, R. M. and Bogner, R. H. (2010) 'Solubility advantage of amorphous pharmaceuticals: I. A thermodynamic analysis', *J. Pharm. Sci.*, 99(3): 1254-1264.
- Musumeci, D., Hunter, C. A., Prohens, R., Scuderi, S. and McCabe, J. F. (2011) 'Virtual cocrystal screening', *Chem. Sci.*, 2(5): 883-890.
- Myz, S. A., Shakhtshneider, T. P., Fucke, K., Fedotov, A. P., Boldyreva, E. V., Boldyrev, V. V. and Kuleshova, N. I. (2009) 'Synthesis of co-crystals of meloxicam with carboxylic acids by grinding', *Mendeleev Commun.*, 19(5): 272-274.
- Nasser, A. and Mingelgrin, U. (2012) 'Mechanochemistry: A review of surface reactions and environmental applications', *Appl. Clay Sci.*, 67-68: 141-150.
- Newman, A., Knipp, G. and Zografi, G. (2012) 'Assessing the performance of amorphous solid dispersions', *J. Pharm. Sci.*, 101(4): 1355-1377.
- Nguyen, K. L., Friščić, T., Day, G. M., Gladden, L. F. and Jones, W. (2007) 'Terahertz time-domain spectroscopy and the quantitative monitoring of mechanochemical cocrystal formation', *Nature Materials*, 6(3): 206-209.
- Oswald, I. D. H., Chataigner, I., Elphick, S., Fabbiani, F. P. A., Lennie, A. R., Maddaluno, J., Marshall, W. G., Prior, T. J., Pulham, C. R. and Smith, R. I. (2009) 'Putting pressure on elusive polymorphs and solvates', *CrystEngComm*, 11(2): 359-366.
- Patil, A. O., Curtin, D. Y. and Paul, I. C. (1984) 'Solid-state formation of quinhydrone from their components. Use of solid-solid reactions to prepare compounds not accessible from solution', *J. Am. Chem. Soc.*, 106(2): 348-53.
- Pedireddi, V. R., Jones, W., Chorlton, A. P. and Docherty, R. (1996) 'Creation of crystalline supramolecular arrays: a comparison of co-crystal formation from solution and by solid-state grinding', *Chemical Communications (Cambridge)*, (8): 987-988.
- Pudipeddi, M. and Serajuddin, A. T. M. (2005) 'Trends in solubility of polymorphs', *J. Pharm. Sci.*, 94(5): 929-939.
- Qiao, N., Li, M., Schlindwein, W., Malek, N., Davies, A. and Trappitt, G. (2011) 'Pharmaceutical cocrystals: An overview', *Int. J. Pharm.*, 419(1-2): 1-11.
- Qiu, Y., Chen, Y. and Zhang, G. G. Z. (2009) *Developing solid oral dosage forms: Pharmaceutical theory and practise*, USA: Academic Press.
- Ralphs, K., Hardacre, C. and James, S. L. (2013) 'Application of heterogeneous catalysts prepared by mechanochemical synthesis', *Chem. Soc. Rev.*, 42(18): 7701-7718.
- Roopwani, R. and Buckner, I. S. (2011) 'Understanding deformation mechanisms during powder compaction using principal component analysis of compression data', *Int. J. Pharm.*, 418(2): 227-234.

- Salager, E., Day, G. M., Stein, R. S., Pickard, C. J., Elena, B. and Emsley, L. (2010) 'Powder Crystallography by Combined Crystal Structure Prediction and High-Resolution 1H Solid-State NMR Spectroscopy', *Journal of the American Chemical Society*, 132(8): 2564-2566.
- Shakhtshneider, T. P. (1997) 'Phase transformations and stabilization of metastable states of molecular crystals under mechanical activation', *Solid State Ionics*, 101-103(Pt. 2): 851-856.
- Shan, N., Toda, F. and Jones, W. (2002) 'Mechanochemistry and co-crystal formation: effect of solvent on reaction kinetics', *Chemical Communications*, (20): 2372-2373.
- Shan, N. and Zaworotko, M. J. (2008) 'The role of cocrystals in pharmaceutical science', *Drug Discovery Today*, 13(9/10): 440-446.
- Shang, N. G., Papakonstantinou, P., Sharma, S., Lubarsky, G., Li, M., McNeill, D. W., Quinn, A. J., Zhou, W. and Blackley, R. (2012) 'Controllable selective exfoliation of high-quality graphene nanosheets and nanodots by ionic liquid assisted grinding', *Chem. Commun.*, 48(13): 1877-1879.
- Shen, J. P., Duan, X. H., Luo, Q. P., Zhou, Y., Bao, Q., Ma, Y. J. and Pei, C. H. (2011) 'Preparation and Characterization of a Novel Cocrystal Explosive', *Cryst. Growth Des.*, 11(5): 1759-1765.
- Smolyakov, V. K., Lapshin, O. V. and Boldyrev, V. V. (2008) 'Mechanochemical synthesis of nanosize products in heterogeneous systems: macroscopic kinetics', *Int. J. Self-Propag. High-Temp. Synth.*, 17(1): 20-29.
- Springuel, G., Norberg, B., Robeyns, K., Wouters, J. and Leyssens, T. (2012) 'Advances in Pharmaceutical Co-crystal Screening: Effective Co-crystal Screening through Structural Resemblance', *Cryst. Growth Des.*, 12(1): 475-484.
- Stahly, G. P. (2007) 'Diversity in Single- and Multiple-Component Crystals. The Search for and Prevalence of Polymorphs and Cocrystals', *Crystal Growth & Design*, 7(6): 1007-1026.
- Stahly, G. P. (2009) 'A Survey of Cocrystals Reported Prior to 2000', *Crystal Growth & Design*, 9(10): 4212-4229.
- Steed, J. W. (2013) 'The role of co-crystals in pharmaceutical design', *Trends Pharmacol. Sci.*, 34(3): 185-193.
- Stojaković, J., Farris, B. S. and MacGillivray, L. R. (2012) 'Vortex grinding for mechanochemistry: application for automated supramolecular catalysis and preparation of a metal-organic framework', *Chem. Commun.*, 48(64): 7958-7960.
- Sun, C. C. and Hou, H. (2008) 'Improving Mechanical Properties of Caffeine and Methyl Gallate Crystals by Cocrystallization', *Cryst. Growth Des.*, 8(5): 1575-1579.
- Takacs, L. (2003) 'M. Carey Lea, the father of mechanochemistry', *Bull. Hist. Chem.*, 28(1): 26-34.
- Takacs, L. (2007) 'The mechanochemical reduction of AgCl with metals revisiting an experiment of M. Faraday', *J. Therm. Anal. Calorim.*, 90(1): 81-84.
- Takacs, L. (2013) 'The historical development of mechanochemistry', *Chem. Soc. Rev.*, 42(18): 7649-7659.
- Thakuria, R., Delori, A., Jones, W., Lipert, M. P., Roy, L. and Rodríguez-Hornedo, N. (2013) 'Pharmaceutical cocrystals and poorly soluble drugs', *Int. J. Pharm.*, 453(1): 101-125.
- Toda, F., Tanaka, K. and Sekikawa, A. (1987) 'Host-guest complex formation by a solid-solid reaction', *J. Chem. Soc., Chem. Commun.*, (4): 279-80.
- Trasi, N. S. and Byrn, S. R. (2012) 'Mechanically Induced Amorphization of Drugs: A Study of the Thermal Behavior of Cryomilled Compounds', *AAPS PharmSciTech*, 13(3): 772-784.
- Trask, A. V. (2007) 'An overview of pharmaceutical cocrystals as intellectual property', *Molecular Pharmaceutics*, 4(3): 301-309.
- Trask, A. V. and Jones, W. (2005) 'Crystal engineering of organic cocrystals by the solid-state grinding approach', *Topics in Current Chemistry*, 254(Organic Solid State Reactions): 41-70.
- Trask, A. V., Motherwell, W. D. S. and Jones, W. (2005a) 'Pharmaceutical cocrystallization: Engineering a remedy for caffeine hydration', *Cryst. Growth Des.*, 5(3): 1013-1021.
- Trask, A. V., Motherwell, W. D. S. and Jones, W. (2006) 'Physical stability enhancement of theophylline via cocrystallization', *Int. J. Pharm.*, 320(1-2): 114-123.

- Trask, A. V., Shan, N., Motherwell, W. D. S., Jones, W., Feng, S., Tan, R. B. H. and Carpenter, K. J. (2005b) 'Selective polymorph transformation via solvent-drop grinding', *Chemical Communications*, (7): 880-882.
- Trask, A. V., van de Streek, J., Motherwell, W. D. S. and Jones, W. (2005c) 'Achieving Polymorphic and Stoichiometric Diversity in Cocrystal Formation: Importance of Solid-State Grinding, Powder X-ray Structure Determination, and Seeding', *Crystal Growth & Design*, 5(6): 2233-2241.
- Trotzki, R., Hoffmann, M. M. and Ondruschka, B. (2008) 'Studies on the solvent-free and waste-free Knoevenagel condensation', *Green Chem.*, 10(7): 767-772.
- Tumanov, I. A., Achkasov, A. F., Boldyreva, E. V. and Boldyrev, V. V. (2011) 'Following the products of mechanochemical synthesis step by step', *CrystEngComm*, 13(7): 2213-2216.
- Urakaev, F. K. and Boldyrev, V. V. (2005) 'Theoretical estimation of conditions for the preparation of nanoscale systems in mechanochemical reactors', *Russ. J. Phys. Chem.*, 79(4): 563-572.
- Wang, G.-W. (2013) 'Mechanochemical organic synthesis', *Chem. Soc. Rev.*, 42(18): 7668-7700.
- Wildfong, P. L. D., Morris, K. R., Anderson, C. A. and Short, S. M. (2007) 'Demonstration of a shear-based solid-state phase transformation in a small molecular organic system: chlorpropamide', *J. Pharm. Sci.*, 96(5): 1100-1113.
- Willart, J. F., Descamps, N., Caron, V., Capet, F., Danede, F. and Descamps, M. (2006) 'Formation of lactose-mannitol molecular alloys by solid state vitrification', *Solid State Communications*, 138(4): 194-199.
- Wood, P. A., Feeder, N., Furlow, M., Galek, P. T. A., Groom, C. R. and Pidcock, E. (2014) 'Knowledge-based approaches to co-crystal design', *CrystEngComm*, 16(26): 5839-5848.
- Wöhler, F. (1844) 'Untersuchungen über das Chinon', *Justus Liebigs Annalen der Chemie*, 51(2): 145-163.
- Yamamoto, K., Tsutsumi, S. and Ikeda, Y. (2012) 'Establishment of cocrystal cocktail grinding method for rational screening of pharmaceutical cocrystals', *Int. J. Pharm.*, 437(1-2): 162-171.
- Yan, D., Delori, A., Lloyd, G. O., Friščić, T., Day, G. M., Jones, W., Lu, J., Wei, M., Evans, D. G. and Duan, X. (2011) 'A Cocrystal Strategy to Tune the Luminescent Properties of Stilbene-Type Organic Solid-State Materials', *Angew. Chem., Int. Ed.*, 50(52): 12483-12486.
- Zhu, S.-E., Li, F. and Wang, G.-W. (2013) 'Mechanochemistry of fullerenes and related materials', *Chem. Soc. Rev.*, 42(18): 7535-7570.
- Šepelák, V., Düvel, A., Wilkening, M., Becker, K.-D. and Heitjans, P. (2013) 'Mechanochemical reactions and syntheses of oxides', *Chem. Soc. Rev.*, 42(18): 7507-7520.
- Štrukil, V., Igrc, M. D., Fábíán, L., Eckert-Maksic, M., Childs, S. L., Reid, D. G., Duer, M. J., Halasz, I., Mottillo, C. and Friščić, T. (2012) 'A model for a solvent-free synthetic organic research laboratory: click-mechanosynthesis and structural characterization of thioureas without bulk solvents', *Green Chem.*, 14(9): 2462-2473.

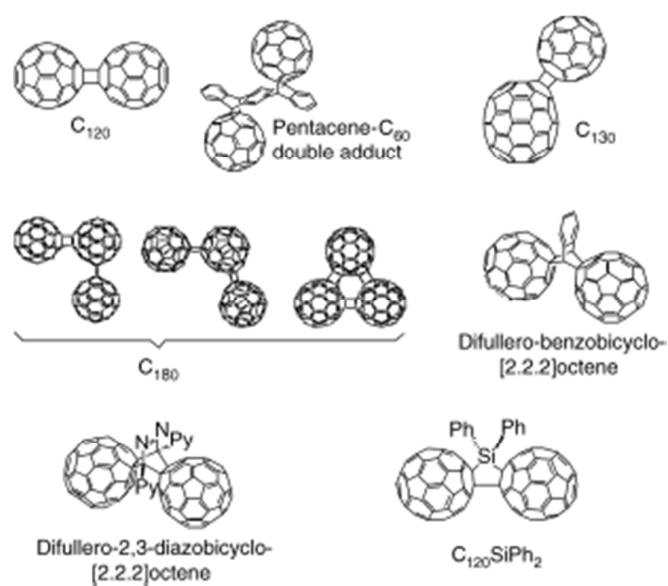


Figure 1. Various fullerene complexes generated by mechanochemical treatment of C_{60} . These products were not obtained from solution reactions. (Braga and Grepioni, 2004)

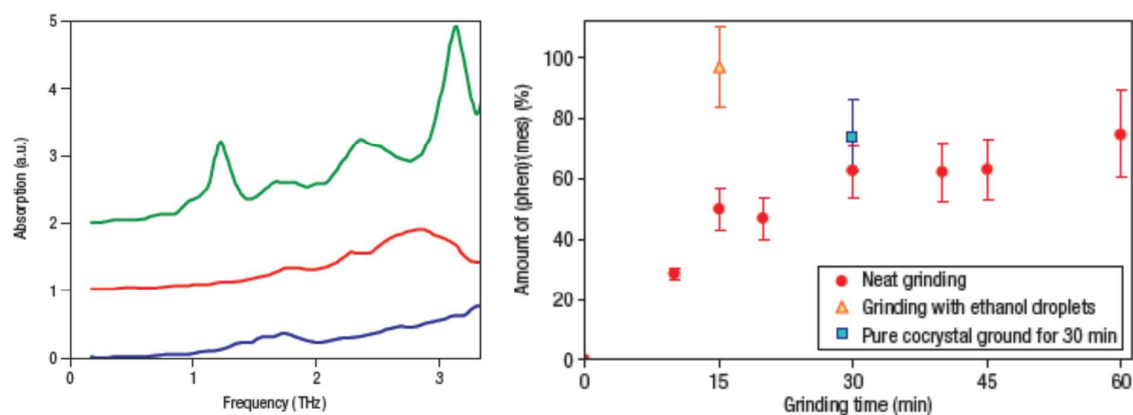


Figure 2. (a) Terahertz spectra obtained from (top to bottom): a 1:1 mesaconic acid-phenazine cocrystal; mesaconic acid; phenazine. (b) Analysis (ex situ) of the extent of formation of the cocrystal from a mixture of phenazine and mesaconic acid, as a function of neat grinding time, as measured using the characteristic cocrystal band at 1.1 THz (red circles). The orange triangle, by comparison, shows close to 100% conversion in 15 minutes as a result of the presence of liquid in a LAG experiment. The blue square represents the percentage of a cocrystal sample that remained crystalline during dry grinding. (Nguyen et al., 2007)

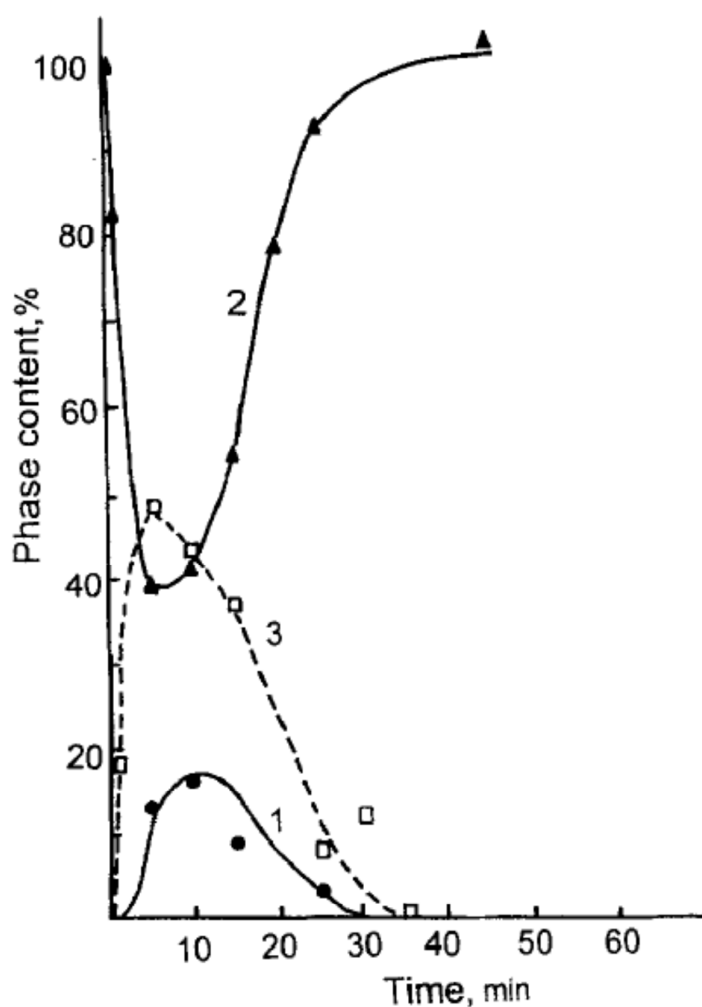
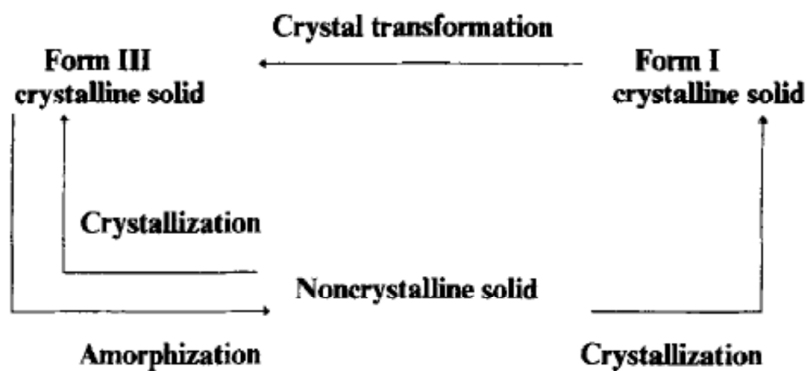


Figure 3. (a) Schematic of the different pathways occurring during the mechanochemical treatment of sulphathiazole. Mechanical treatment resulted in the partial amorphisation of the drug and the interconversion of Forms I and II. (b) Time profile for the phase interconversion for sulphathiazole: (1) – indicating generation of Form I, (2) initial loss and subsequent regeneration of Form III, (3) the existence of a transient amorphous phase. (Shakhtshneider, 1997)

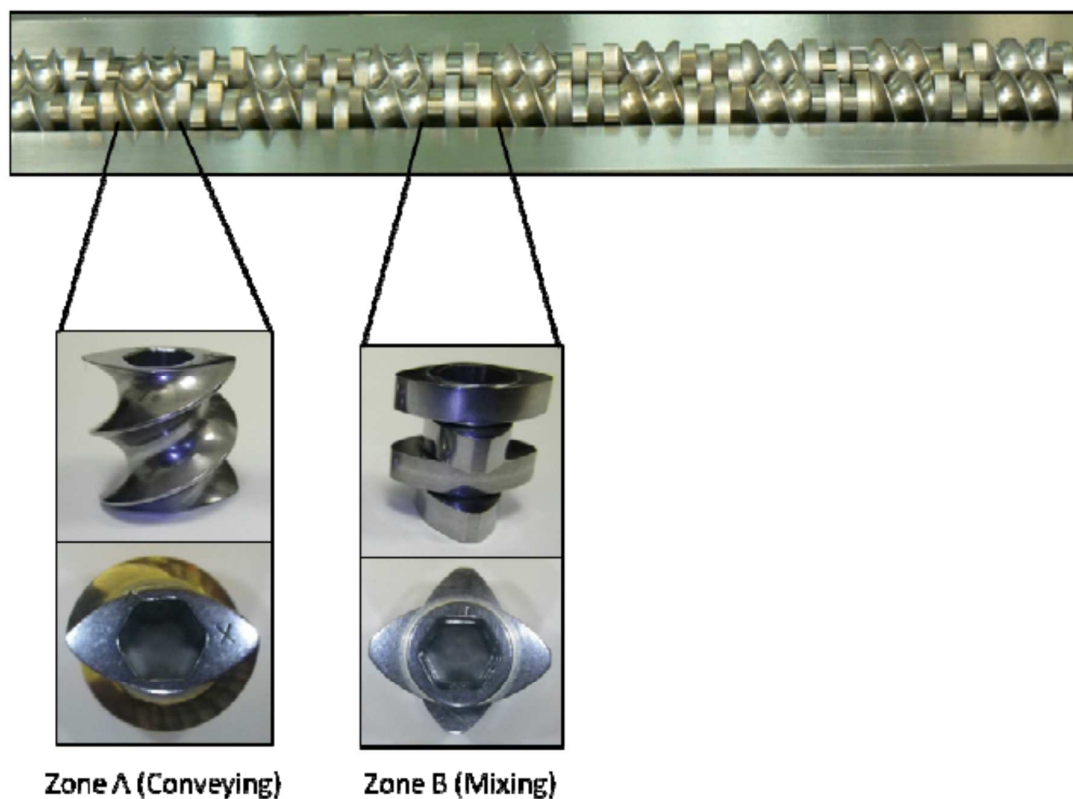


Figure 4. Typical twin extrusion configuration used for the formation of cocrystals. The conveying and mixing zones are shown. Typical output rate is approximately $0.5 \text{ g}\cdot\text{min}^{-1}$. PXRD suggests comparable properties for the product to that obtained by conventional solution growth. The possibility of simultaneously blending the cocrystal product within a polymer matrix is an important additional advantage of the method.(Daurio et al., 2011)

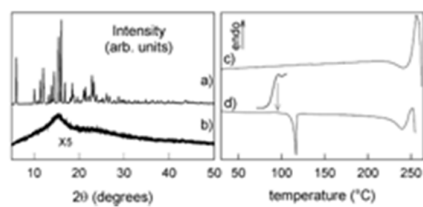


Figure 5. Demonstration of the amorphisation of trehalose as a result of milling at room temperature within a high energy planetary micro-mill. (a and b) PXRD and (c and d) DSC data before and after milling. (Descamps et al., 2007)

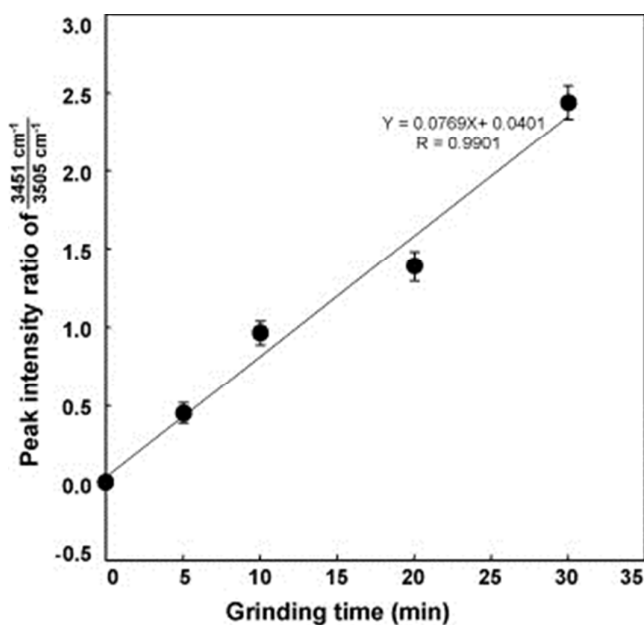
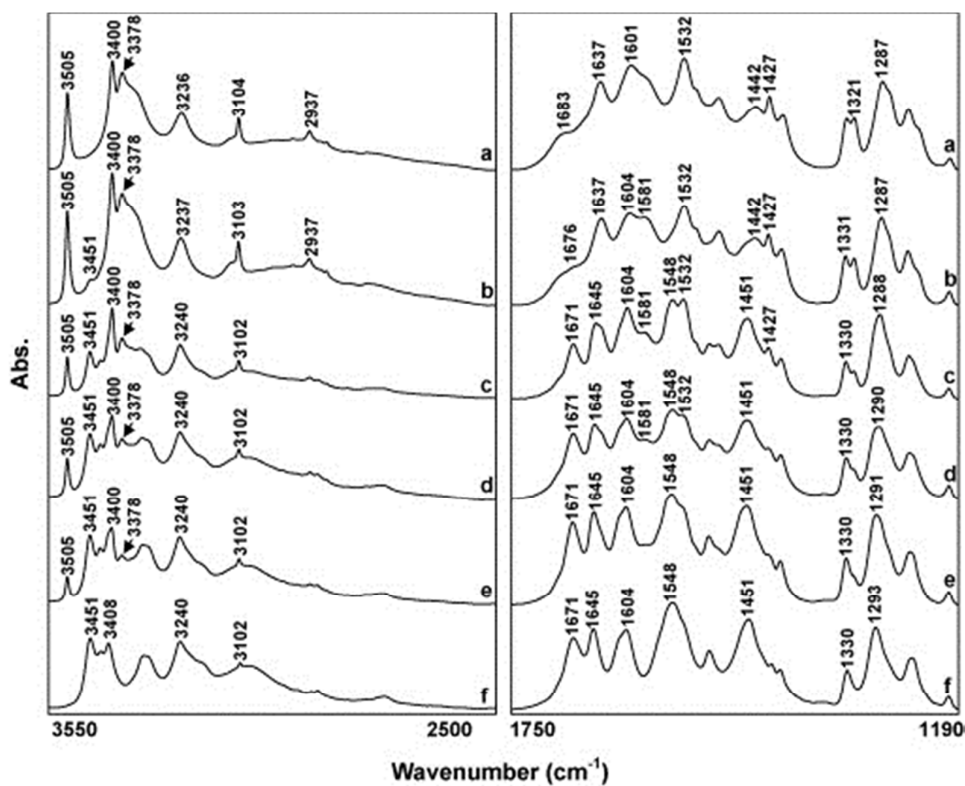


Figure 6. (a) Grinding-time dependence of the FTIR spectra for famotidine showing from top to bottom the emergence of the absorption at 3451 cm^{-1} which is used to monitor the formation of Form A of the material. (b) Plot of peak intensity ratio (I_{3451}/I_{3505}) for the spectra above indicating a possible zero order rate law for the conversion. (Lin et al., 2006)

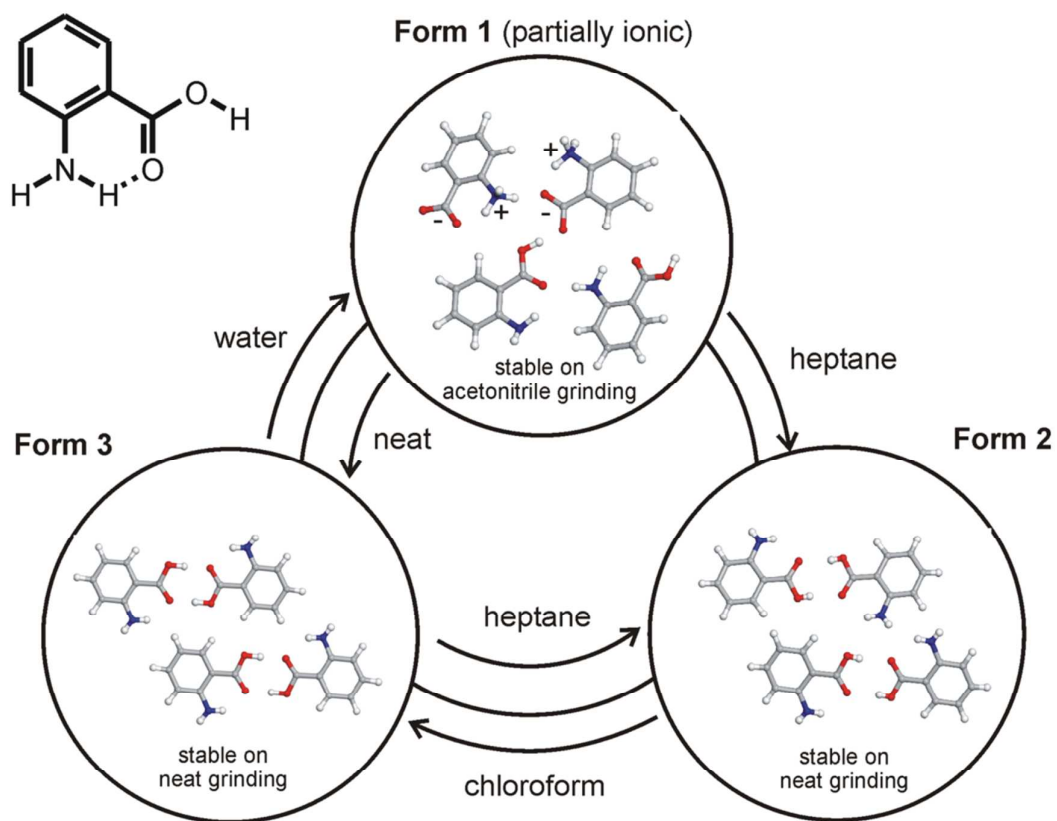


Figure 7. Schematic of the observed transformations between the three polymorphic forms of anthranilic acid with the pathways depending on the conditions under which mechanochemical treatment was performed.

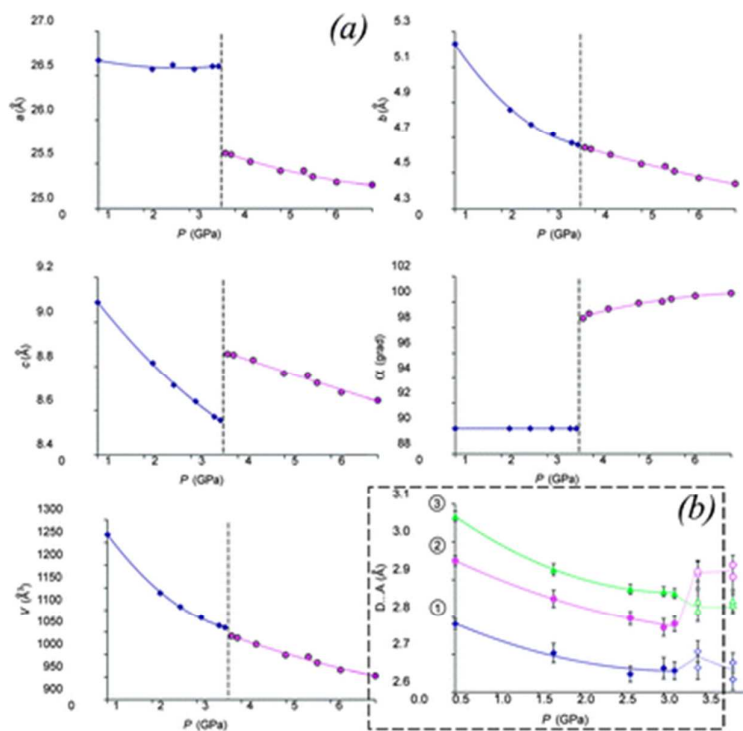


Figure 8. (a) Hydrostatic pressure induced transition for chlorpropamide in a saturated ethanol solution. The phase change results in a first order change at approximately 3.5 GPa. (b) Changes in non-hydrogen atom positions as the transition pressure is reached. (Boldyreva, 2013)

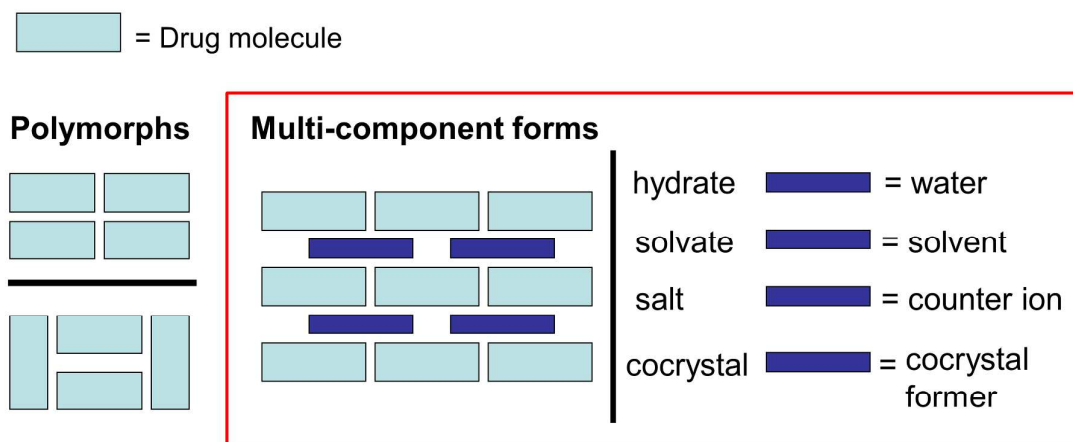


Figure 9. Schematic of the characteristics of polymorphs and multicomponent systems. Cocrystals represent a sub-set of the multicomponent group, frequently that characterised by the requirement that the components be neutral and solid at room temperature.

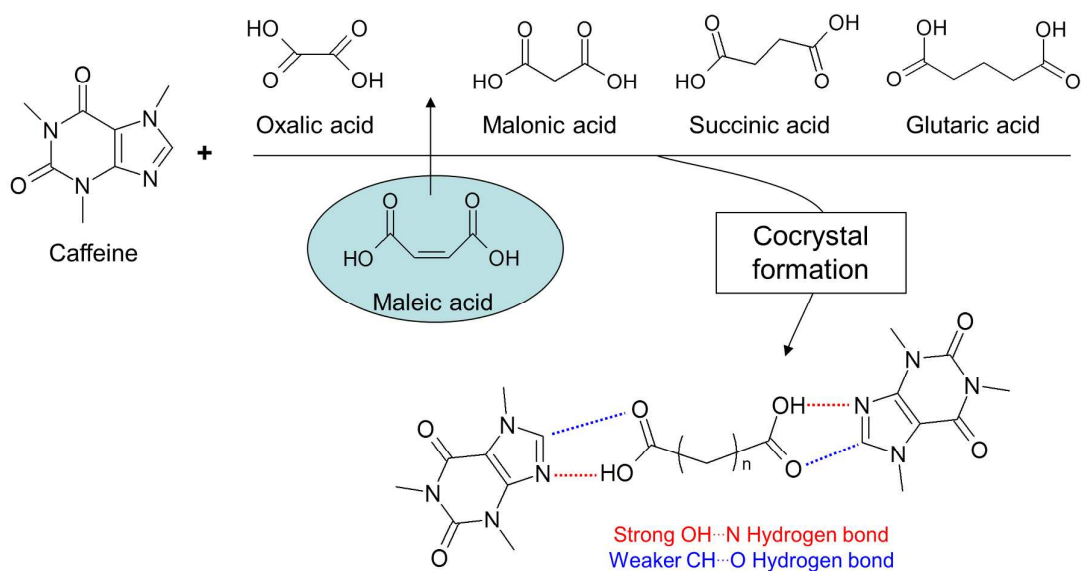


Figure 10. Supramolecular synthon approach used in the design of cocryystals of caffeine with various dicarboxylic acids. This approach lead to a variety of solid forms of caffeine which could be tested for stability under conditions of high humidity. Mechanochemistry was the technique used to both screen for cocryystal formation and also prepare powders for humidity assessment.

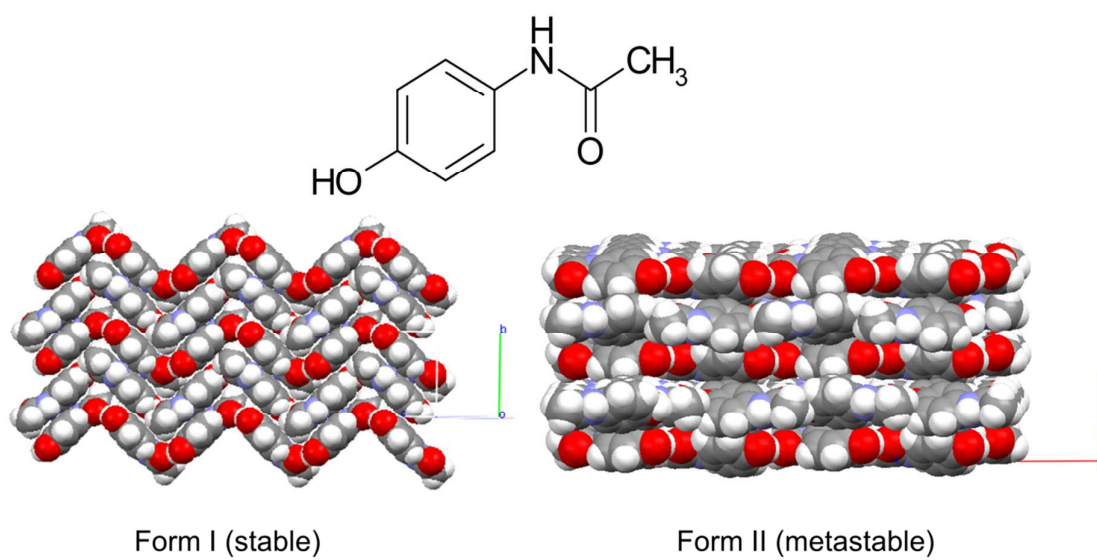


Figure 11. Packing diagrams for Form I and Form II paracetamol. Whilst Form I is the stable phase it does not compress well during tablet formation. The metastable Form II has a layered structure more appropriate for compression, but readily transforms to Form I.

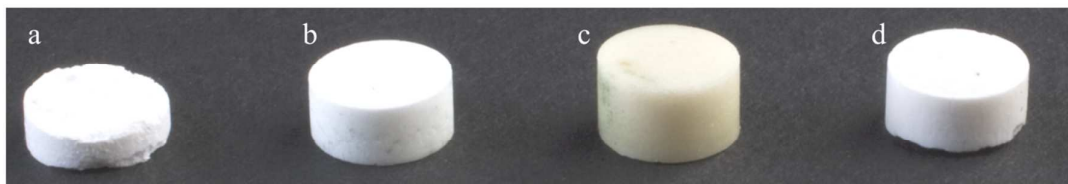


Figure 12. Micrographs of tablets made from (a) paracetamol Form I and (b to d) cocrystals of paracetamol with theophylline, naphthalene and oxalic acid respectively. Tablet (a) is poorly formed as a result of the inappropriate packing of the molecules in the lattice, whereas the cocrystal structures are amenable to deformation during tableting.(Karki et al., 2009a)

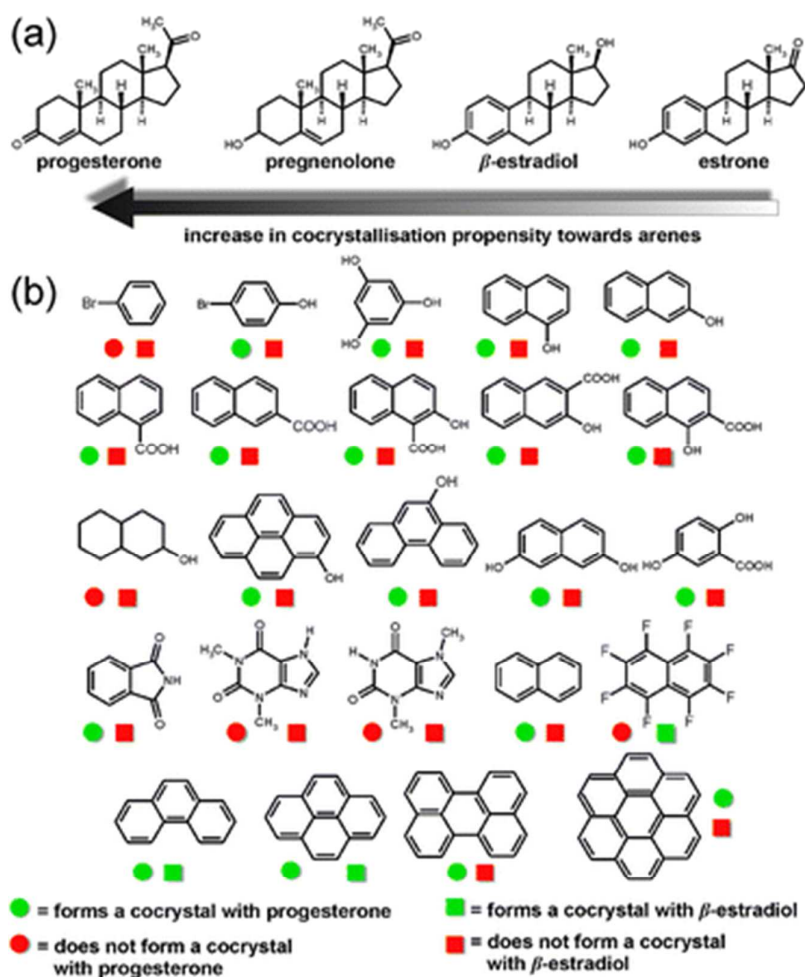


Figure 13. The use of mechanochemistry to explore the various possible combinations of coformers for a family of steroid drugs. The various outcomes are delineated by the accompanying legend. (Friščić et al., 2010a)

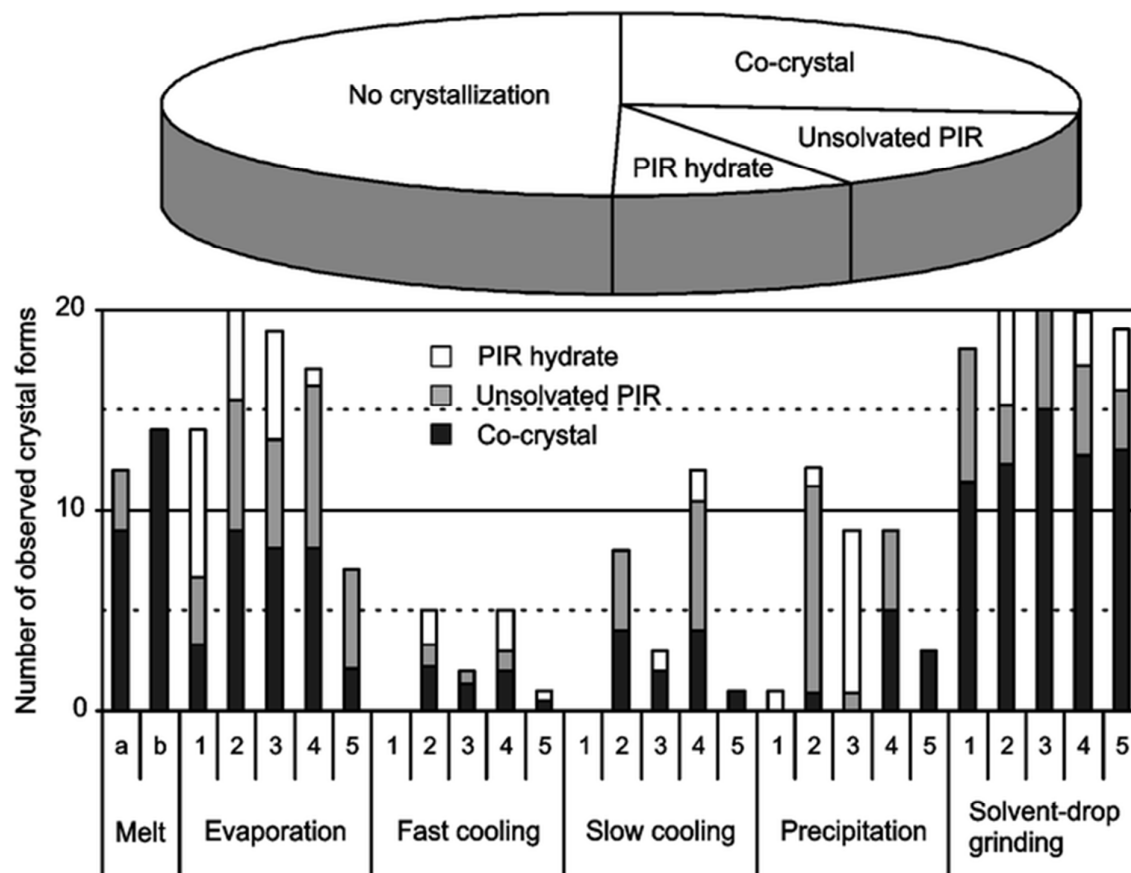


Figure 14. Overview of the results obtained by various cocrystallisation attempts for piroxicam. Solvent-drop grinding (LAG) is shown in this case to be the most efficient and straightforward screening method. The numbers 1-5 indicate the various solvents used in the experiments.(Fucke et al., 2012)

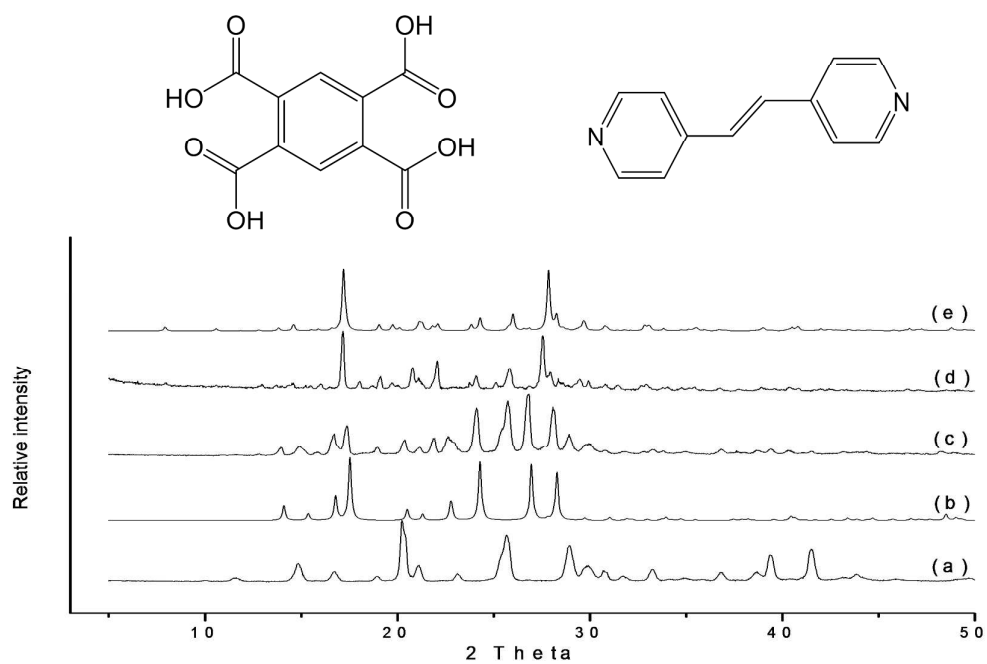


Figure 15. Demonstration of the enhanced kinetics of cocystal formation upon addition of a few drops of methanol to the grinding jar. PXRD patterns for (a) tetracarboxylic acid, (b) bipyrindyl, (c) outcome of neat grinding for 60 minutes (as the sum of the reactants), (d) the product obtained when a few drops of methanol are added and (e) the simulated pattern for the cocystal.

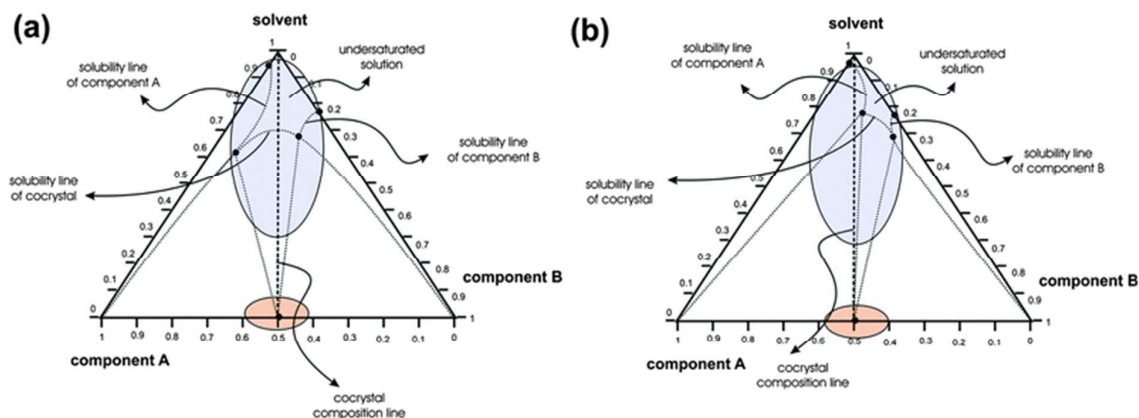


Figure 16. Typical three-component phase diagrams contrasting (a) congruent and (b) incongruent solubility profiles indicating the difficulties which will arise during conventional evaporative solution growth crystallisation. The fact that LAG experiments, with minimal amounts of solvent present, places the system close to the cocystal composition illustrates the ability of LAG to form cocystals when solids of very different solubility are investigated. (Delori et al., 2012)

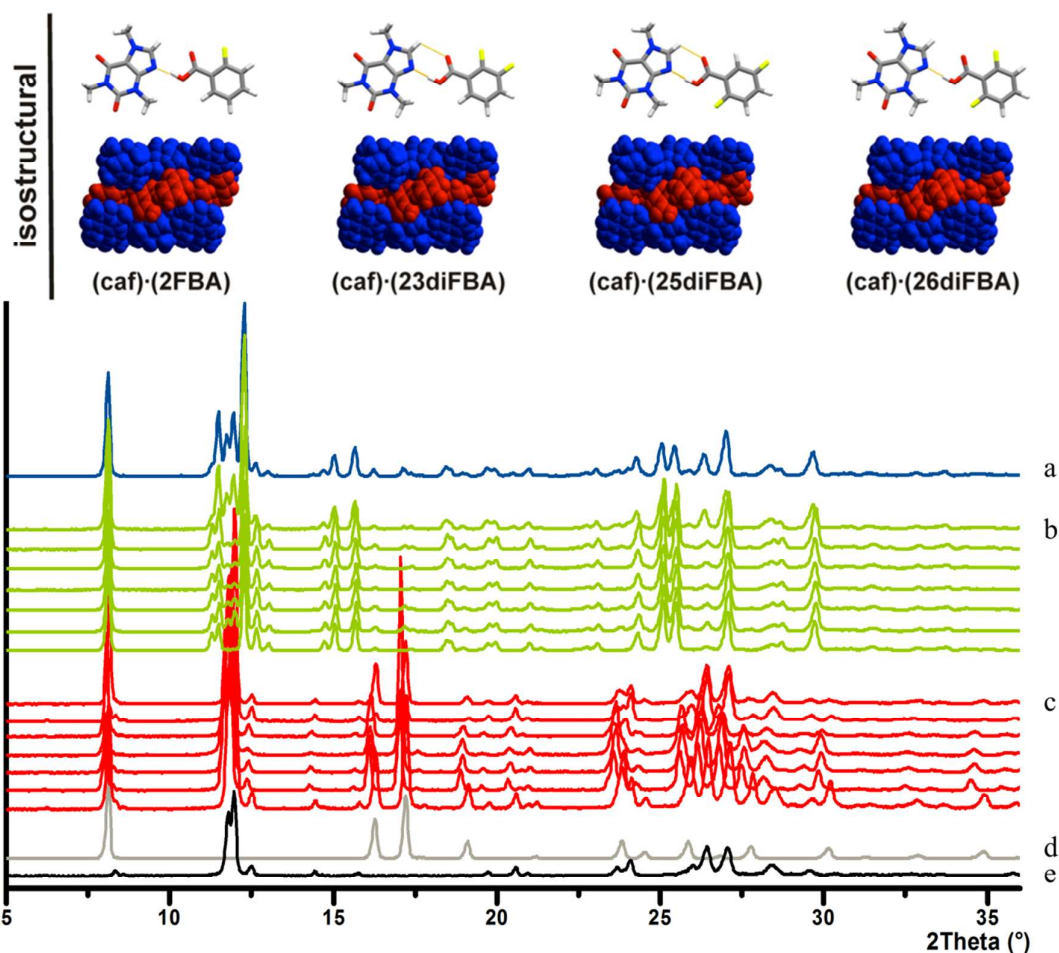


Figure 17. Top. Isostructural cocrystals of caffeine with various fluorobenzoic acids which have similar packing to that predicted for the likely structure for the caffeine-benzoic acid cocrystal. Bottom. PXRD traces of (a) product without deliberate addition of seeds, but prepared in an environment where the caffeine-benzoic acid cocrystal had previously been obtained, (b) products of various seeding reactions, (c) products of various unseeded reactions, (d) benzoic acid and (e) caffeine. The main points to note include the similarity of the patterns in (a) and (b) and that those in (c) are a simple combination of the starting materials in (d) and (e). (Bučar et al., 2013a)

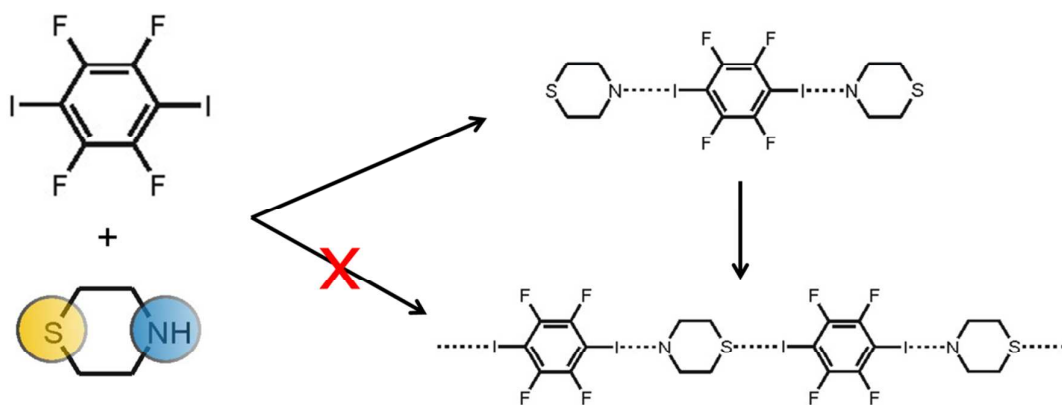


Figure 18. The discrete trimer units and extended polymer chains (based on halogen bond interactions) believed to be formed during the LAG reaction. When the strength of the halogen bond is weak the product is limited to the trimer unit.

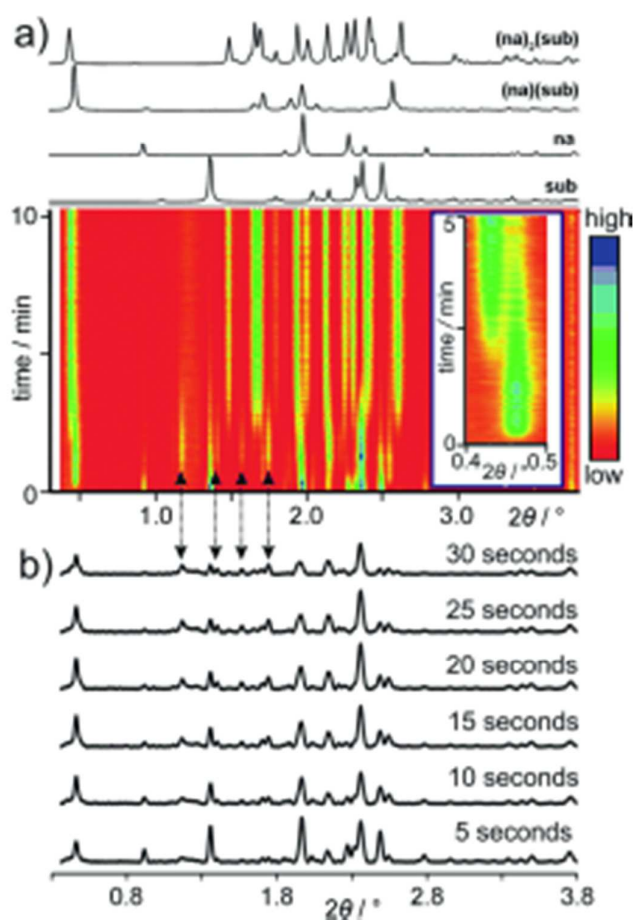


Figure 19. *In situ* synchrotron data for the milling of suberic acid and nicotinamide in a 2:1 ratio. (a) The PXRD patterns of the phases expected to be formed during milling along with the data obtained as a function of time. The inset shows the particular region at 0.4 to 0.5 degrees two-theta showing the initial formation of the 1:1 cocrystal followed by the 2:1 product. (b) The specific reflections indicated by arrows indicate the intermediate phase which is not detected by conventional *ex situ* studies. (Halasz et al., 2013)

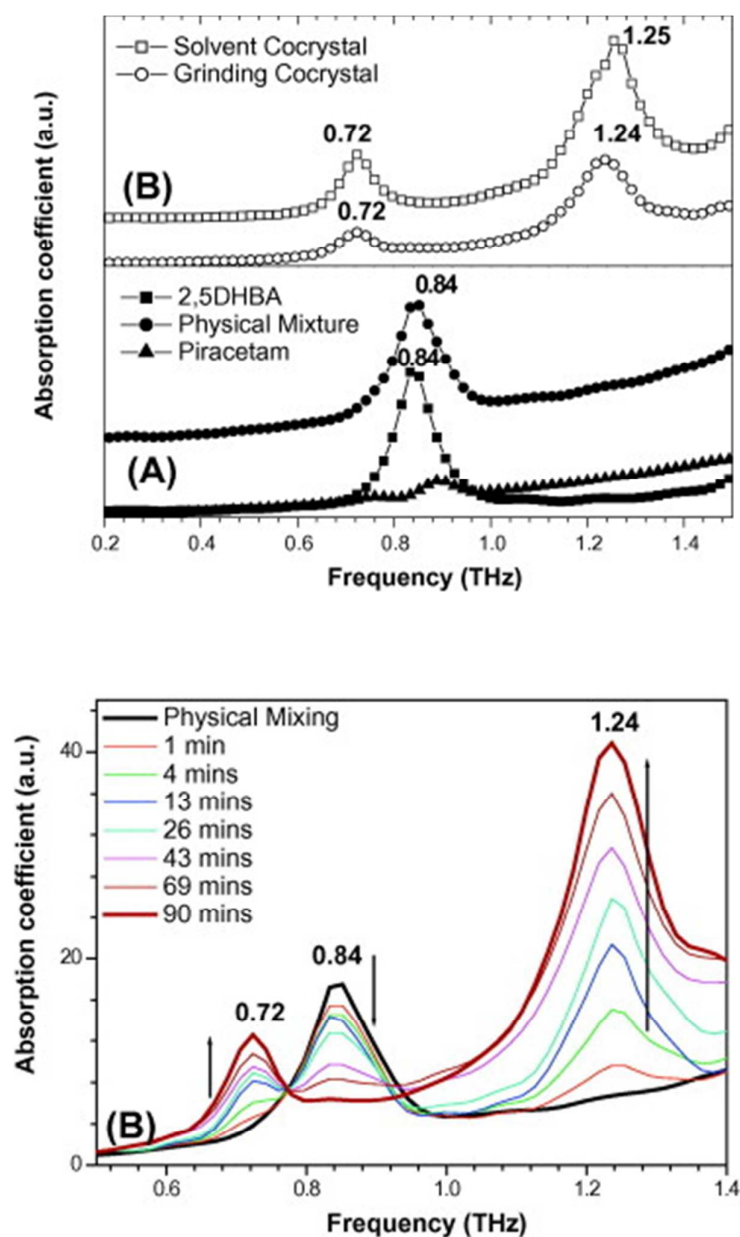


Figure 20. (Top) THz spectra obtained for the system 2,5-dihydroxybenzoic acid (DHBA) and piracetam. (A) Spectra for DHBA, piracetam and a physical mixture. (B) Comparison of the spectra resulting from cocryystals obtained by solvent evaporation and neat grinding. (Bottom) Frequency-domain spectra as a function of grinding time from 1 – 90 minutes. The gradual loss of the line at 0.84 and emergence of the lines at 0.72 and 1.24 THz is associated with formation of cocryystal. (Du et al., 2013)

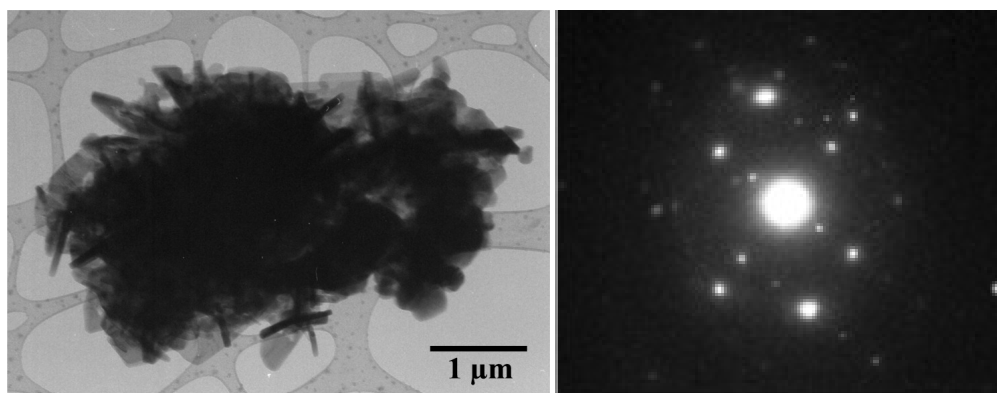


Figure 21. (a) Transmission electron micrograph and (b) electron diffraction pattern obtained from a sample of a theophylline:L-malic acid cocrystal prepared by LAG. The method is able to monitor particle size as well as polymorphic form.(Eddleston et al., 2010)

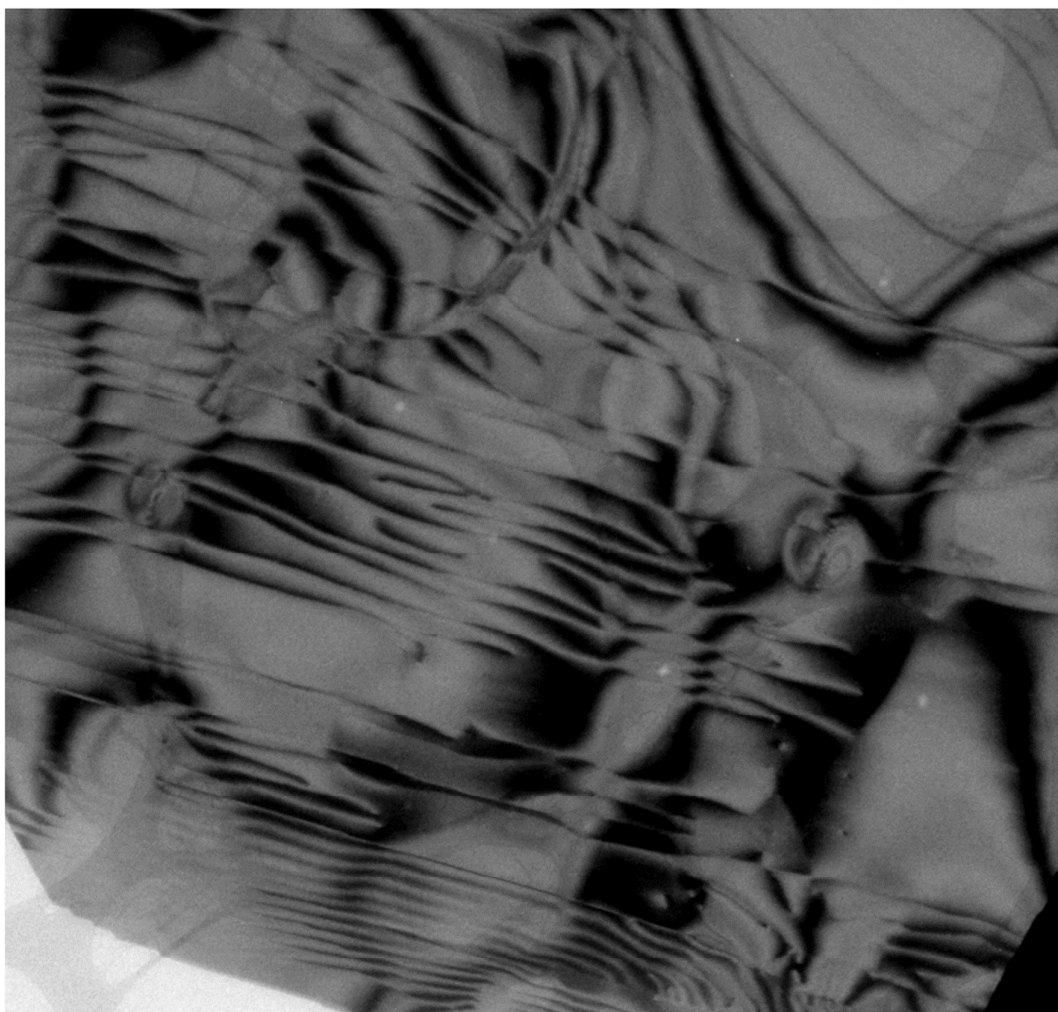


Figure 22. Extensive network of dislocations in a sample of theophylline as revealed by transmission electron microscopy. In general, such dislocations can result from the mechanical treatment of crystals.