

**BiFeO₃/YSZ bilayer electrolyte for low temperature solid oxide fuel cell**

Journal:	<i>RSC Advances</i>
Manuscript ID:	RA-ART-03-2014-001862.R1
Article Type:	Paper
Date Submitted by the Author:	11-Apr-2014
Complete List of Authors:	Tu, Yu-Chieh; National Taiwan University, Department of Materials Science and Engineering Chang, Chun-Yu; National Taiwan University, Department of Materials Science and Engineering Wu, Ming-Chung; Chang Gung University, Department of Chemical and Materials Engineering Shyue, Jing-Jong; National Taiwan University, Department of Materials Science and Engineering; Academia Sinica, Research Center for Applied Sciences Su, Wei-Fang; National Taiwan University, Materials Science and Engineering

ARTICLE

BiFeO₃/YSZ bilayer electrolyte for low temperature solid oxide fuel cell

Cite this: DOI: 10.1039/x0xx00000x

Yu-Chieh Tu,^a Chun-Yu Chang,^a Ming-Chung Wu,^b Jing-Jong Shyue^{a,c} and Wei-Fang Su^{*a}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

We have demonstrated BiFeO₃ (BFO) as a potential bilayer electrolyte for 650°C low temperature solid oxide fuel cell application. The stoichiometric perovskite BFO is synthesized by wet chemistry, calcined at 500°C and sintered at 850°C. The crystalline structure is confirmed by X-ray diffraction spectroscopy, the atomic ratios (Bi:Fe) of 1.02 and 1.00 are determined by X-ray energy dispersive spectroscopy and inductively coupled plasma-mass spectroscopy respectively. The X-ray photoelectron spectroscopy analysis indicates the presence of oxygen vacancies which can partially reduce Fe³⁺ and result in relatively high dielectric constant (6252 at 100 kHz) and ionic conductivity (> 10⁻² S·cm⁻¹ at 650°C). The BFO is coated with yttria-stabilized zirconia (YSZ) protective layer to avoid hydrogen reduction of BFO. This bilayer electrolyte exhibits 1.6 times increasing in maximum power density as compared with pure YSZ when Ni-YSZ anode and lanthanum strontium cobalt ferrite (LSCF) cathode are used in the fuel cell at 650°C.

Introduction

The solid oxide fuel cell (SOFC) is one of the promising clean energy sources in 21st century.¹⁻⁵ At present, yttria stabilized zirconia (8 mole % Y₂O₃ in ZrO₂, YSZ) electrolyte has been widely used in the SOFC due to its high ionic conductivity, good chemical and mechanical stability.^{6,7} However, the SOFC using YSZ electrolyte has to be operated at high temperature of >700°C.⁸ The high operation temperature consumes energy to maintain it and requires expensive high temperature resistant interconnects.^{9,10} Thus, there is urgent need to develop new electrolyte material that has high ionic conductivity at low temperature of 650°C or below. Recently, bismuth based materials have been identified as good low temperature electrolytes due to the ease of ionization of bismuth.¹¹⁻¹³ The fluorite-type bismuth oxides such as Er doped Bi₂O₃ (ESB)¹⁴, Dy₂O₃/WO₃-doped Bi₂O₃ (DWSB),¹⁵ Bi₄YbO_{7.5}¹⁶ were reported as low temperature solid oxide electrolytes for fuel cell. However, they contain very expensive rare element. The low cost perovskite BiFeO₃ (BFO) would be a good candidate for low cost and low temperature oxide electrolyte because ionic radius of Bi and Fe are large to accommodate oxygen vacancies for high ionic conductivity. The BFO is a rhombohedrally distorted perovskite structure with ferroelectricity and antiferromagnetism, and widely used in gas sensors, data storage, microelectronic devices, and visible-light photocatalyst.¹⁷⁻²² The perovskite BFO can be prepared using various methods such as solid state reaction process,²³⁻²⁷ pulsed layer deposition,²⁸ epitaxial growth¹⁷ and sol-gel synthesis.²⁹ It is difficult to synthesize pure phase BFO using solid state reaction process due

to the formation of second phase. The second phase can be etched away by nitric acid²⁴ or reduced by a rapid liquid phase sintering process at 880°C.²⁵ In this study, we report a stoichiometry controlled BFO powder was synthesized by low cost solution method and then sintered at 850°C to obtain pure perovskite structure. We demonstrate the BFO powder can be fabricated into a bilayer electrolyte (YSZ coated BFO) for the use of 650°C fuel cell.

Experimental details

The chemicals and materials were used as received without further purification including bismuth nitrate pentahydrate (Lot: MKBG7332V, 98%, Aldrich), iron nitrate nonahydrate (Lot: STBC2273V, 98%, Aldrich), 2-ethoxyethanol (Lot: A0298235, 99%, Acros), acetic acid (Lot: J15805, J. T. Baker), polyvinyl alcohol binder (PVA, Lot: MKBD2298, 80%, Aldrich), ZrO₂-8% mole Y₂O₃ powder (YSZ, Tosoh Corporation), nickel oxide powder (NiO, Alfa Aesar), graphite powder (Lot: H24X012, 99.9999%, Alfa Aesar), α -terpineol (Alfa Aesar), ethyl cellulose (Acros), lanthanum strontium cobalt ferrite (LSCF) slurry (La_{0.6}Sr_{0.4}Co_{0.2}Fe_{0.8}O_{3- δ} , Fuel Cell Materials Corporation), and silver paste (TED PELLA).

The BFO was synthesized using excess Bi at a composition of Bi/Fe=1.05/1.00 to compensate the volatility of bismuth during the sintering process. In a 500 ml three neck flask, 10.1865 g (0.021 mole) of bismuth nitrate pentahydrate and 8.0805 g (0.020 mole) of iron nitrate nonahydrate were dissolved in a mixture of 200 ml of 2-ethoxyethanol and 200 ml of acetic acid at 70°C for 30 min in Ar to obtain a clear yellow

brown BFO precursor solution. The BFO precursor solution was dried at 120°C overnight to obtain BFO powder. The BFO was calcined in air by heating it to 500°C at 10°C·min⁻¹ and then kept at 500°C for 2 hrs to obtain calcined powder. After grinding and sieving, the calcined BFO powder has an average particle size of 177 nm which was determined by dynamic light scattering method (3000 HAS Zetasizer, Malvern Instrument). A combined instrument (SDT-Q600, TA Instrument) of thermogravimetric analyzer (TGA) and differential scanning calorimetry (DSC) was used to determine the decomposition temperature of organic component and the phase transition temperature of BFO respectively. The 6.6 mg of as-synthesized BFO was heated from room temperature to 825°C at 10°C·min⁻¹ in air to obtain the thermal behaviors of BFO.

Disks with and without PVA were fabricated for the characterization of sintered BFO. For the disk containing PVA, the 500 mg of calcined powder was mixed with 1.0 wt.% PVA binder, and pressed into a disk of 10 mm in diameter under a uniaxial force of 20 kg·cm⁻³ for 20 sec, and then 50 kg·cm⁻³ for 2 min. The BFO disk was sintered from room temperature (RT) to 550°C at 2°C·min⁻¹ and then kept at 550°C for 4hrs in air to remove PVA. And then the disk was heated further from 550°C to higher temperature e.g., 750°C, 800°C, 850°C, and 900°C at 1°C·min⁻¹, respectively and kept at that temperature for 4 hrs. At the end of holding time, the power of furnace was switched off and the sintered disk was naturally cooled inside the furnace. The sintered BFO disk was used for the measurement of density and dielectric constant. For the disk without PVA, the same sintering processes was used, the sample was used for determining its crystalline structure, morphology, ionic conductivity and power density.

The experimental density of different BFO disks was measured by using Archimedes' method. The relative density of BFO disk was calculated basis on the theoretical density of 8.346 g·cm⁻³ by assuming a rhombohedral distorted perovskite structure.³⁰ The crystal structure of BFO disks was determined by X-ray diffraction spectrometry (XRD) (Rigaku, TTRAXIII) using Cu K_α radiation at 50 kV and 300 mA. XRD patterns were collected from 2θ between 20 and 70 with a 0.005° step at 5°·min⁻¹. The morphology of BFO disks were studied by scanning electron microscopy (SEM) (JEOL, JSM-6510). Inductively coupled plasma-mass spectrometry (ICP-MS) (7500ce, Agilent, Japan) and X-ray energy dispersive spectrometry (EDS) attached to SEM were used to determine the ratio of Bi to Fe in the sintered BFO. The X-ray photoelectron spectrometry (XPS) (ULVAC-PHI, Chigasaki, Japan) was used to examine the core-levels of BFO disk by using Al K_α radiation with a photoelectron take off angle of 45° in high vacuum (~10⁻⁷ torr). The relative dielectric constant and dielectric loss were measured by using inductance-capacitance-resistance (LCR) (Wayne Kerr 6420) meter at 10 kHz and 100 kHz frequencies respectively.

A direct current four-probe configuration was used for the measurement of ionic conductivity using Teraoka's method.^{31,32} The multilayer sample of Ag/LSCF/YSZ/BFO/YSZ/LSCF/Ag was used for the measurement. The preparation of each layer is

described in the following. The BFO layer was prepared by pressing BFO calcined powder in a rectangular mold with a dimension of 0.4×0.4×4.5 cm³ first and then sintered at 850°C for 4 hours. The two YSZ layers were made from plates with the dimension of 0.4×0.4×0.1 cm³ which were prepared respectively by pressing YSZ powder under a uniaxial force of 10 kg·cm⁻³ for 10 sec in a mold, then sintered the samples from room temperature to 1400°C at a rate of 2°C·min⁻¹ and held at this temperature for 4 hrs. The 40-50 micron of LSCF was screened printed on each YSZ plate to make LSCF coated YSZ plates and sintered from room temperature to 850°C at 5°C·min⁻¹ and then kept at 850°C for 4hrs in air. Then all the layer parts were clamped together into a sample holder and connected to the Keithley 2410 electrometer by silver wires for ionic conductivity measurement at a constant current of 10 mA in the temperature range of 823~973 K.

The electromotive force (EMF) was used to determine the ionic transport number (*t_i*) accordingly to the literature.³³ The sample was fabricated by depositing 150 nm thin platinum electrode on both side of 1.1 mm thick BFO disk and then sintered at 850°C and connected to the voltage/ampere meter using silver wire for measurements. The *t_i* was measured from 200°C to 650°C using gradient oxygen concentration, one side is air (pO₂=0.21atm) and the other side is pure oxygen (pO₂=1.00atm). The *t_i* can be obtained from the ratio of the measured emf (*E_{exp}*) and theoretical Nernst voltage (*E_{th}*) as shown in equation 1.

$$t_i = \frac{E_{exp}}{E_{th}} \quad (1)$$

The fuel cell has a multilayer structure of anode/protective layer YSZ/BFO/cathode which is fabricated by step-wise procedure to ensure high mechanical strength without cross contamination. The procedure was described in the following. For the anode of fuel cell, 0.8 g of YSZ powder, 1.2 g of nickel oxide powder and 0.2 g of graphite powder were first milled for 1h to prepare Ni-YSZ powder. The 300 mg of Ni-YSZ powder were pressed into a disk of 14 mm diameter under a uniaxial force of 40 kg cm⁻³ for 60 sec, and then an YSZ protective layer was coated on the top of disk by spinning YSZ slurry at 6000 rpm for 60 sec. To form the stable YSZ slurry, 7.8 g of YSZ powder, 0.5 g of ethyl cellulose and 17.0 g of α-terpineol were mixed and ball milled for two days. The assembled anode was sintered from RT to 1400°C at 2°C·min⁻¹ and then kept at 1400°C for 4 hrs in air. For the electrolyte layer of BFO, the 500°C calcined BFO powder was mixed first with 93.0g of α-terpineol and 7.0 g of ethyl cellulose. The resulting BFO slurry was coated onto the anode by casting. The BFO coated anode was dried at RT and then sintered to 850°C at 2°C·min⁻¹ and then kept at 850°C for 4hrs in air. Then, the LSCF cathode layer was coated by screen printing on top of BFO layer using lanthanum strontium cobalt ferrite (LSCF) slurry to finish the assembly of fuel cell. The assembled fuel cell was sintered from RT to 850°C at 5°C·min⁻¹ and then kept at 850°C for 2hrs in air. The final sintered fuel cell has the structure of Ni-YSZ/YSZ/BFO/LSCF at the thickness of

550 μm /17 μm /30 μm /44 μm , respectively. The thickness of YSZ electrolyte in the pure YSZ cell is 18 μm .

Results and discussion

We prepared perovskite BFO using a simple solution method. The BFO powder was synthesized first by reacting bismuth nitrate and iron nitrate in a mixture of 2-ethoxyethanol and acetic acid at 70 $^{\circ}\text{C}$ for 30 min and dried at 120 $^{\circ}\text{C}$ overnight. To control the stoichiometry of the BFO, the raw material molar ratio of Bi/Fe at 1.05/1.00 was used to compensate the volatility of bismuth during the sintering process. As shown in Fig. 1, the BFO powder started to lose weight at 162 $^{\circ}\text{C}$ (black TGA curve) and indicated the first rapid weight loss at 206 $^{\circ}\text{C}$ (blue DSC curve) which were due to the elimination of water from polyvinyl alcohol binder. The second rapid weight loss at 276 $^{\circ}\text{C}$ (DSC curve) was due to the rupture of carbon-hydrogen bond and carbon-carbon bond. The third peak of the DSC curve at 400 $^{\circ}\text{C}$ was the residual carbon changed to carbon dioxide.³⁴The fourth exothermic peak at 800 $^{\circ}\text{C}$ (DSC curve) was due to the crystallization of BFO.

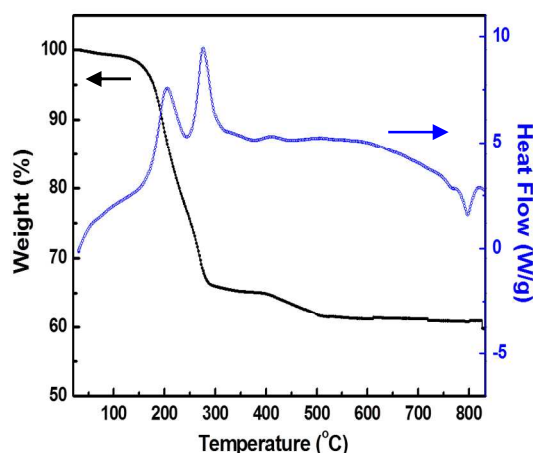


Fig. 1 TGA and DSC curves of BFO powder.

According to the results of thermal analysis, we calcined BFO powder at 500 $^{\circ}\text{C}$ for two hours before any further thermal treatment. To study the crystallization behaviour and optimal sintering temperature of BFO, the calcined powder was thermally treated at different temperature and the results are shown in Fig. 2. The perovskite BFO already formed in the calcined powder with iron rich impurity of $\text{Bi}_2\text{Fe}_4\text{O}_9$ (JCPDS No.721832). The purity of BFO was improved further upon heat treatment at higher temperature. After 800 $^{\circ}\text{C}$ treatment, the good quality of crystal was formed with minute bismuth rich impurity of $\text{Bi}_{36}\text{Fe}_2\text{O}_{57}$ (JCPDS No.420181). A pure perovskite BFO was obtained for sample sintered at either 850 $^{\circ}\text{C}$ or 900 $^{\circ}\text{C}$.

The changes of BFO densification were monitored by measuring the density of each sample sintered at different temperature and shown in Fig. 3. A close to 92% of theoretical density was achieved for the 850 $^{\circ}\text{C}$ sample. The morphology changes of samples at different temperature were studied by

SEM as shown in Fig. 4. The results indicated the grain sizes of samples were increased and the porosity was decreased after increasing the sintering temperature.

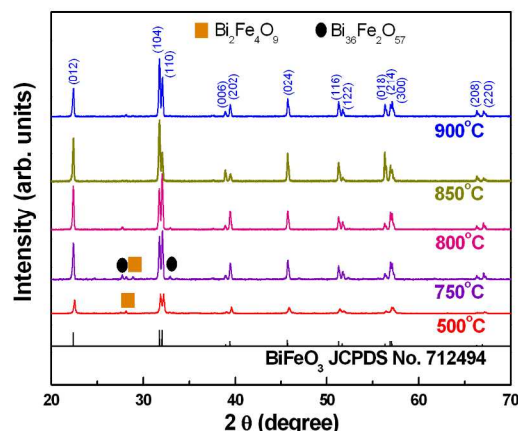


Fig. 2 XRD patterns of BFO samples prepared at different temperature.

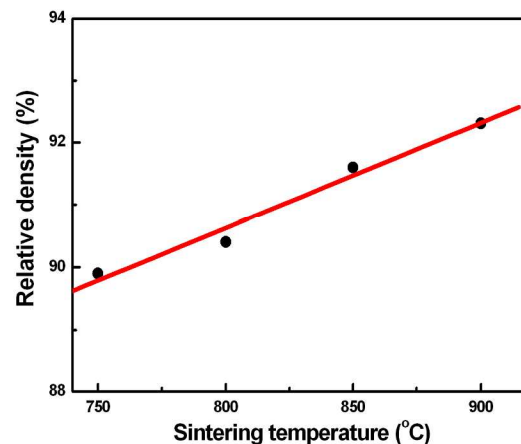


Fig. 3 Relative density (fitted spectra: red solid line) of BFO samples prepared at different temperature.

The chemical composition of BFO was initially studied by EDS for samples sintered at different temperature. For the 750 $^{\circ}\text{C}$ sample, the ratio of Bi/Fe is the same as the reactants at 1.05. However, the ratio was decreased to close to 1.00 for the 900 $^{\circ}\text{C}$ sample. The elemental analysis of EDS is usually biased toward the heavier element. The analysis of Bi/Fe ratio was further studied by more accurate ICP-MS analysis. The results indicate the stoichiometry ratio of 1.00 was achieved after thermal treatment at 850 $^{\circ}\text{C}$. The physical and chemical characteristics of BFO samples prepared at different temperature are summarized in Table 1.

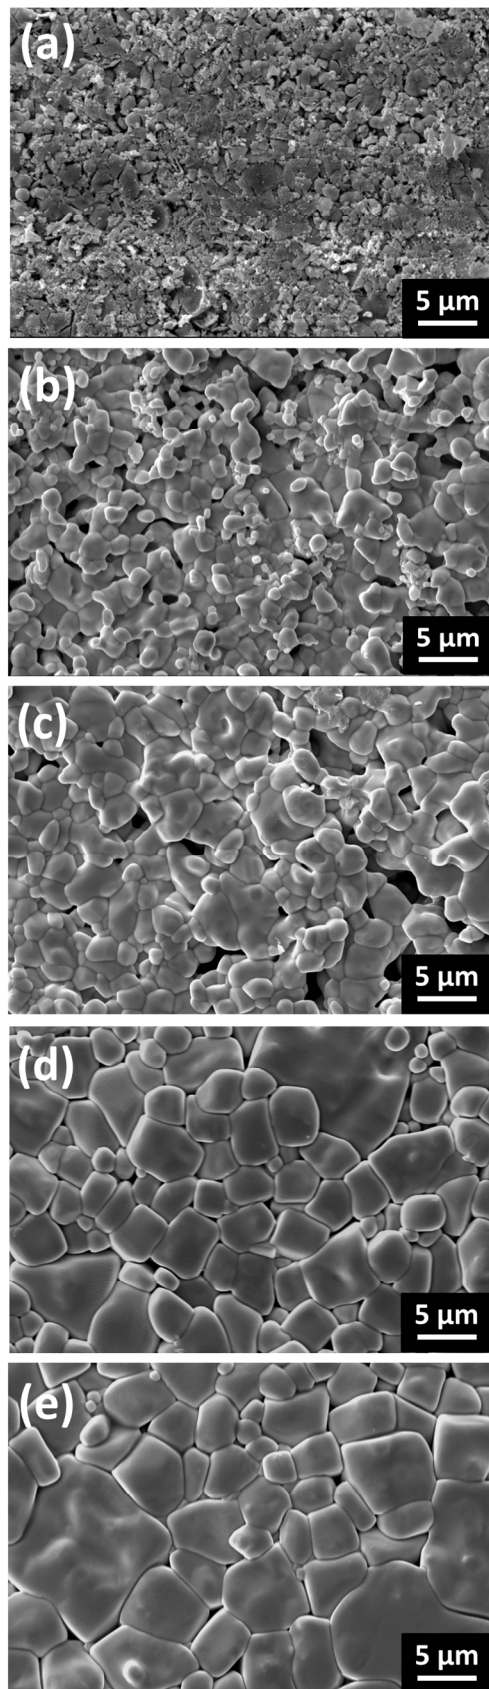


Fig. 4 SEM images of BFO samples prepared at different temperature: (a) 500°C, (b) 750°C, (c) 800°C, (d) 850°C, and (e) 900°C.

Table 1 Characteristics of BFO samples prepared at different temperature.

Temperature (°C)	Density (g/cm ³)	Grain size (μm)	Atomic ratio of Bi/Fe by EDS, and ICP-MS in parentheses
750	7.510	1.75	1.05
800	7.553	2.46	1.04, (1.01)
850	7.649	4.50	1.02, (1.00)
900	7.708	6.04	1.01

The oxygen binding energies of the BFO after different temperature treatment were investigated by XPS and the results are shown in Fig. 5. The O1s binding³⁵ of BFO at 529 eV is clearly observed for all samples. It is interested to note that oxygen vacancy (V_o^{2+}) at 532 eV was also present in all samples. The oxygen vacancy may be produced from the removal of OH^- , NO_3^- during the sintering process,³⁶ it was reduced somewhat with increasing sintering temperature above 500°C. It is known the amount of oxygen vacancies is directly related to the conductivity of electrolyte.³⁷ However, the sample sintered at 500°C did not form pure perovskite BFO with high density. High quality electrolyte should have high density to minimize the potential gas crossover, so the samples sintered at 850°C and 900°C were evaluated for the application of electrolyte.

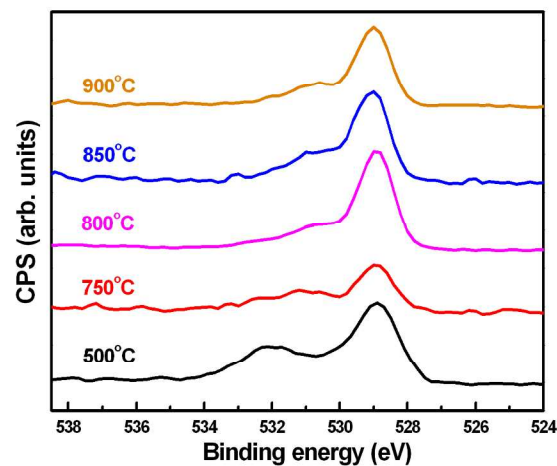



Fig. 5 XPS spectra of O1s binding energy of BFO samples prepared at different temperature.

The iron binding energies³⁸ of BFO prepared at different temperature were further investigated by XPS as shown in Fig. 6. The measured curve was fitted under a linear background black dash-dot line between 62.8 eV and 50 eV. Fig. 6 clearly shows two characteristic peaks appearing at 55.6 eV for Fe^{3+} and 53.8 eV for Fe^{2+} , respectively. These results show the coexistence of Fe^{3+} and Fe^{2+} is easily formed in our samples due to the presence of oxygen vacancy according to the following reaction.



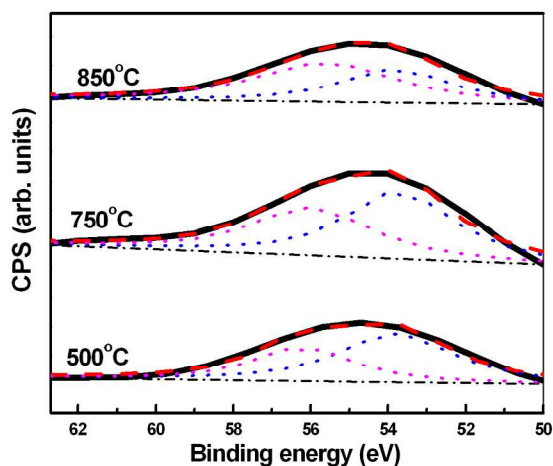


Fig. 6 XPS spectra (measured spectra: black solid lines, fitted spectra: red dash lines) of Fe3p binding energy of BFO samples prepared at different temperature.

The distorted structure of BFO results in high dielectric constant in the range of several hundred depending on the preparation method. We measured the dielectric constant and dielectric loss of our solution method prepared BFO samples sintered at different temperature and the results are summarized in Table 2. It was worth noting they all exhibit rather high dielectric constant and dielectric loss as compared with conventional solid state method and thin film deposition method. The results can be deduced from the presence of high oxygen vacancy in our samples as shown in the XPS study. The abnormal high dielectric constant and loss may suggest the material may have high ionic mobility.

Table 2 Dielectric constant and dielectric loss of BFO samples prepared at different temperature.

Temperature (°C)	Dielectric constant at 10 kHz	Dielectric loss at 10 kHz	Dielectric constant at 100kHz	Dielectric loss at 100 kHz
750	3443	0.11	3027	0.44
800	3459	0.16	2940	0.59
850	7477	0.18	6252	0.52
900	7355	0.19	6104	0.47

The material requirements for high ionic conductivity solid oxide electrolyte material are (1) available empty sites, and (2) low energy barrier for ions to hop.³⁷ The ionic mobility of material can be expressed by two kinds of values: ionic conductivity^{31,32} and ionic transport number.³³ We measured the changes of ionic transport number from 200°C to 650°C and ionic conductivity from 550°C to 700°C for the BFO samples sintered at 850°C. The sample sintered below or above this temperature was not used due to the impurity presence in the former and the high energy usage in the later. Fig. 7 shows the ionic transport number approaches 0.99 at 650°C which indicates the BFO is ionized at this temperature. Fig. 8 shows

the ionic conductivity of BFO is $7.9 \times 10^{-2} \text{ S}\cdot\text{cm}^{-1}$ at 650°C. The plot of $\ln(\sigma T)$ vs. $1000/T$ is linear which can be expressed by Arrhenius equation³⁹ as shown in Equation 3.

$$\sigma = \frac{A}{T} \exp\left(-\frac{E_{a,\text{ion}}}{kT}\right) \quad (3)$$

Where σ is the ionic conductivity, T is the absolute temperature, k is the Boltzmann constant, A is the pre-exponential factor, and $E_{a,\text{ion}}$ is the ionic activation energy. Thus, the ionic activation energy of BFO can be determined from the slope of the plot to be 0.69 eV which is lower than the ionic activation energy of YSZ of 1.01 eV.³⁹ Thus, the BFO should be a good electrolyte material for low temperature SOFC due to its relatively high ionic conductivity at 650°C and low ionic activation energy.

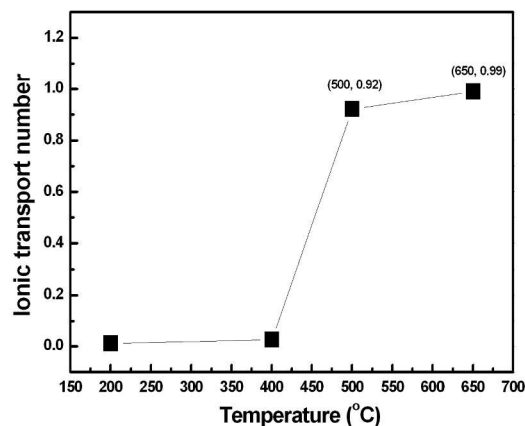


Fig. 7 Plot of oxygen transport number versus temperature for BFO sample prepared at 850°C.

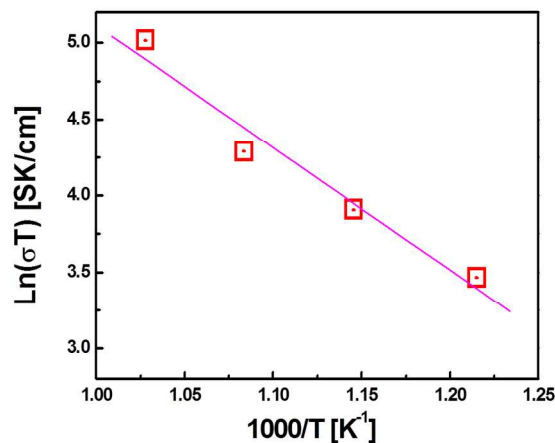


Fig. 8 Plot of ionic conductivity versus temperature for BFO sample prepared at 850°C.

We found the fuel cell fabricated from the BFO only electrolyte exhibited both low open-circuit voltage and low power density as shown in Fig. S1 of supporting information. The Bi content of BFO was reduced from 18 at.% to 2.74 at.% without YSZ layer after the fuel cell operated at 700°C (Table

S1). The large amount of Bi^{3+} in BFO was changed to Bi and separated from BFO upon hydrogen exposure; the grain size of BFO become much smaller as shown in the SEM study (Fig. S2). Thus, we made a functionally graded bilayer electrolyte by placing a hydrogen inert layer of YSZ on the top of BFO layer to protecting it from contacting with hydrogen. Here, the YSZ serves dual functions: protective layer and electrolyte layer. The fuel cell was assembled from Ni-YSZ anode, YSZ/BFO bilayer electrolyte, and lanthanum strontium cobalt ferrite (LSCF) cathode. Fig. 9 (a) and Fig. 9 (b) show the cross-sectional SEM photos of the fuel cell using YSZ electrolyte and BFO electrolyte. The thickness of YSZ/BFO bilayer electrolyte is $17\mu\text{m}/30\mu\text{m}$. The performance of fuel cells with and without BFO was measured at 500°C , 550°C , 600°C , 650°C and 700°C respectively. The results are shown in Fig. 10. At 500°C as expected, the maximum power density of YSZ/BFO electrolyte solar cell has been improved as compared with pure YSZ electrolyte which is consistent with the results of oxygen transport number study. However, both samples exhibits low power density in the range of $14\text{-}50\text{ mWcm}^{-2}$. The power density of fuel cell with the BFO/YSZ was increased when the operating temperature increasing above 500°C . At 650°C , it has shown more than 1.6 times increase in power density as compared with the fuel cell with YSZ only. In the present configuration of fuel cell with BFO/YSZ, the actual electrolyte is BFO and the YSZ serves as a protective layer only. The result is very promising and suggests the solution method prepared BFO electrolyte has potential application for low temperature solid oxide fuel cell. As indicates in Fig. 10, the open-circuit voltage (OCV) of YSZ/BFO electrolyte is lower than pure YSZ electrolyte which may be from the minute reduction of Bi^{3+} of BFO to Bi. When we increased the thickness of YSZ layer from ~ 17 micron to ~ 100 micron, the open circuit voltage remained above 1.0 V but the power density was decreased from 175 mW/cm^2 to 45 mW/cm^2 at 650°C (Fig. S3). That is due to poor ionic conductivity of YSZ dominating the performance of fuel cell. To reach both high power density and high open-circuit voltage of BFO fuel cell, it is possible using more densified thin YSZ protective layer and higher ionic conductivity of novel doped BFO.

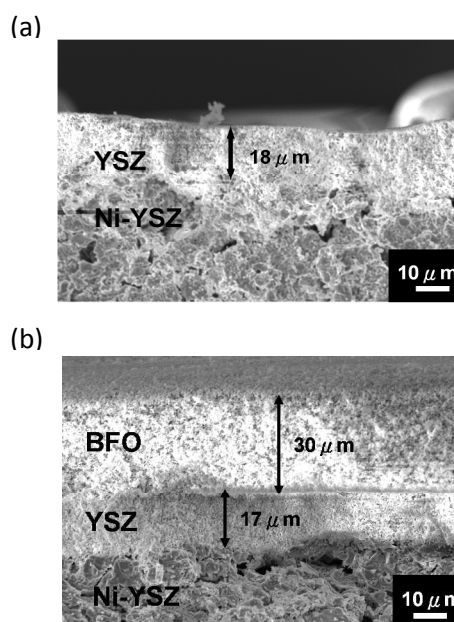


Fig. 9 Cross-sectional SEM photos of fuel cell with (a) YSZ electrolyte and (b) YSZ /BFO electrolyte.

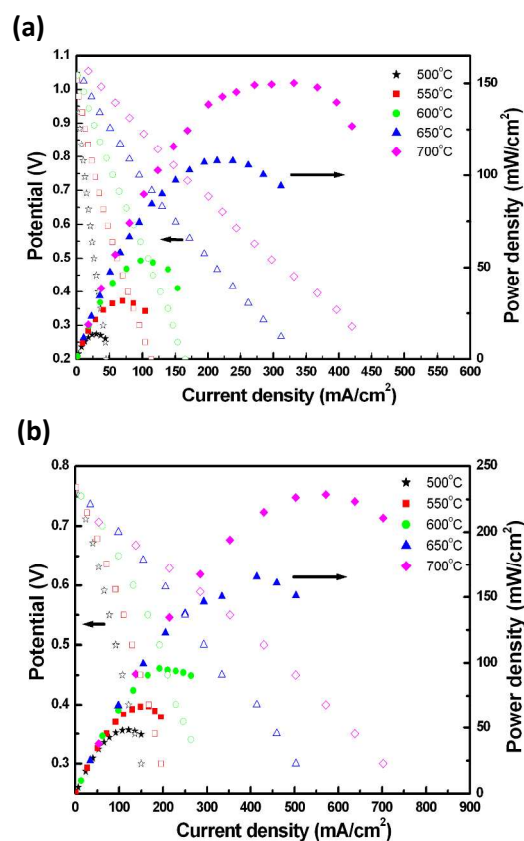


Fig. 10 Comparison of fuel cells performance with (a) YSZ electrolyte and (b) YSZ/BFO electrolyte at different operating temperature.

Conclusion

We have successfully demonstrated the low cost solution method to prepare BFO which has potential application as electrolyte for low temperature solid oxide fuel cell. The BFO powder was first prepared using bismuth nitrate and iron nitrate in a mixture of 2-ethoxyethanol and acetic acid at 70°C. The optimal sintering temperature of BFO was determined to be 850°C which shows the material is in pure perovskite structure, 92% densification, the Bi/Fe ratio of 1.00, ionic conductivity of $7.9 \times 10^{-2} \text{ S}\cdot\text{cm}^{-1}$ at 650°C and ionic activation energy of 0.69 eV. The sintered BFO exhibits high oxygen vacancy that results in high dielectric constant and high ionic conductivity. The fuel cell was assembled from Ni-YSZ anode, YSZ/BFO bilayer electrolyte, and lanthanum strontium cobalt ferrite cathode. The maximum power density of fuel cell with YSZ/BFO electrolyte was increased by 1.6 times as compared with pure YSZ electrolyte. The power density could be improved further using high ionic conductivity novel doped BFO.

Acknowledgements


The authors thank the National Science Council of Taiwan (101-2120-M-002-003, and 102-3113-P-002-027) for financial support of this research.

Notes and references

- ^a No. 1, Sec. 4, Roosevelt Road, Department of Materials Science and Engineering, National Taiwan University, Taipei 10617, Taiwan. Fax: +886 2 33664078; Tel: +886 2 33664078; E-mail: suwf@ntu.edu.tw
- ^b No. 259, Wen-Hwa 1st Road, Department of Chemical and Materials Engineering, Chang Gung University, Taoyuan 333-02, Taiwan.
- ^c No. 128, Sec. 2, Academia Road, Research Center for Applied Sciences, Academia Sinica, Taipei 11529, Taiwan.
- S. D. Souza, S. J. Visco and L. C. D. Jonghe, *Solid State Ion.*, 1997, **98**, 57.
 - J. P. P. Huijsmans, F. P. F. V. Berkel and G. M. Christie, *J. Power Sources*, 1998, **71**, 107.
 - B. C. H. Steele, *Solid State Ion.*, 2000, **129**, 95.
 - Z. Jiang, L. Zhang and L. Cai, C. Xia, *Electrochimica Acta*, 2009, **54**, 3059.
 - E. D. Wachsman and K. T. Lee, *Science*, 2011, **334**, 935.
 - Y. Z. Xing, C. J. Li, C. X. Li and G. J. Yang, *J. Power Sources*, 2008, **176**, 31.
 - B. Li, J. Zhang, T. Kaspar, V. Shutthanandan, R. C. Ewing and J. Lian, *Phys. Chem. Chem. Phys.*, 2013, **15**, 1296.
 - J. Wang, Z. Lu, K. Chen, X. Huang, N. Ai, J. Hu, Y. Zhang and W. Su, *J. Power Sources*, 2007, **164**, 17.
 - B. C. H. Steele and A. Heinzl, *Nature*, 2001, **414**, 345.
 - M. A. Laguna-Bercero, *J. Power Sources*, 2012, **203**, 4.
 - A. M. Azad, S. Larose and S. A. Akbar, *J. Mater. Sci.*, 1994, **29**, 4135.
 - P. Ravindran, R. Vidya, A. Kjekshus, H. Fjellvag and O. Eriksson, *Phys. Rev. B*, 2006, **74**, 224412.
 - K. Brinkman, T. Iuima and H. Takamura, *Jpn. J. Appl. Phys.*, 2007, **46**, L93.
 - E. D. Wachsman, P. Jayaweera, N. Jiang, D.M. Lowe and B.G. Pound, *J. of the Electrochemical Soci.*, 1997, **144**, 233.
 - D. W. Jung, K. L. Duncan and E. D. Wachsman, *Acta Materialia*, 2010, **58**, 355.
 - M. Leszczynska, X. Lin, W. Wrobel, M. Malys, M. Krynski, S. T.

- Norberg, S. Hull, F. Krok and I. Abrahams, *Chem. of Mater.*, 2013, **25**, 326.
- B. J. Zeches, M. D. Rossell, J. X. Zhang, A. J. Hatt, Q. He, C.-H. Yang, A. Kumar, C. H. Wang, A. Melville, C. Adamo, G. Sheng, Y.-H. Chu, J. F. Ihlefeld, R. Erni, C. Ederer, V. Gopalan, L. Q. Chen, D. G. Schlom, N. A. Spaldin, L. W. Martin and R. Ramesh, *Science*, 2009, **326**, 977.
- A. S. Poghosian, H. V. Abovian, P. B. Avakian, S. H. Mkrtchian and V. M. Haroutunian, *Sensors and Actuators*, 1991, **B 4**, 545.
- M. Bibes and A. Barthelemy, *Nat. Mater.*, 2008, **7**, 425.
- F. Gao, X. Chen, K. Yin, S. Dong, Z. Ren, F. Yuan, T. Yu, Z. Zou and J. M. Liu, *Adv. Mater.*, 2007, **19**, 2889.
- C. Hengky, X. Moya, N. D. Mathur and S. Dunn, *RSC Adv.*, 2012, **2**, 11843.
- S. Mohan and B. Subramanian, *RSC Adv.*, 2013, **3**, 23737.
- Y. Ding, T. H. Wang, W. C. Yang, T. C. Lin, C. S. Tu, Y. D. Yao and K. T. Wu, *IEEE Trans. Magn.*, 2011, **47**, 513.
- M. M. Kumar, V. R. Palkar, K. Srinivas and S. V. Suryanarayana, *Appl. Phys. Lett.*, 2000, **76**, 2764.
- Y. P. Wang, L. Zhou, M. F. Zhang, X. Y. Chen and J. M. Liu, *Appl. Phys. Lett.*, 2004, **84**, 1731.
- S. T. Zhang, M. H. Lu, D. Wu, Y. F. Chen and N. B. Ming, *Appl. Phys. Lett.*, 2005, **87**, 262907.
- M. S. Bernardo, T. Jardiel, M. Peiteado, A. C. Caballero and M. Villegas, *J. Am. Ceram. Soc.*, 2011, **31**, 3047.
- J. Wang, J. B. Neaton, H. Zheng, V. Nagarajan, S. B. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D. G. Schlom, U. V. Waghmare, N. A. Spaldin, K. M. Rabe, M. Wuttig and R. Ramesh, *Science*, 2003, **299**, 1719.
- Y. Wang, Q. H. Jiang, H. C. He and C. W. Nan, *Appl. Phys. Lett.*, 2006, **88**, 142503.
- Z. Dai and Y. Akishige, *J. Phys. D: Appl. Phys.*, 2010, **43**, 445403.
- Y. Teraoka, H. M. Zhang, K. Okamoto and N. Yamazoe, *Mater. Res. Bull.*, 1988, **23**, 51.
- K. Eguchi, T. Setoguchi, T. Inoue and H. Arai, *Solid State Ion.*, 1992, **52**, 165.
- M. J. Verkerk, K. Keizer and A. J. Burggraaf, *J. Appl. Electrochem.*, 1980, **10**, 81.
- W. F. Su, Principles of Polymer Design and Synthesis, Springer, 2013, Chapter 5.
- L. Fang, J. Liu, S. Ju, F. Zheng, W. Dong and M. Shen, *Appl. Phys. Lett.*, 2010, **97**, 242501.
- A. Y. Kim, S. H. Han, H.-W. Kang, H.-G. Lee, J. S. Kim and C. I. Cheon, *Ceram. Inter.*, 2012, **38S**, S397.
- Anthony R. West, Basic Solid State Chemistry, Wiley, 2002, Second Edition, Chapter 7
- T. Yamashita and P. Hayes, *Appl. Surf. Sci.*, 2008, **254**, 2441.
- M. B. Suresh and R. Johnson, *Inter. J. Ener. Res.*, 2012, **36**, 1291-1297.

Graphical Abstract

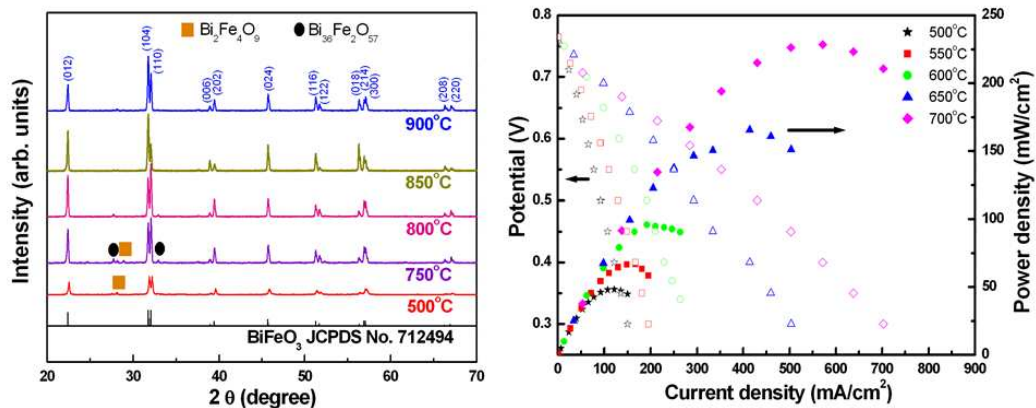

High crystalline perovskite BiFeO₃ is obtained by a facile solution method. We have reported that YSZ/BFO electrolyte with 17μm/30μm thickness, respectively, showed a maximum power density of 165 mW/cm² and open-circuit voltage of 0.75 V at 650°C.