RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This Accepted Manuscript will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the **Information for Authors**.

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard <u>Terms & Conditions</u> and the <u>Ethical guidelines</u> still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.




Entry for the Table of Contents

Combined Heterogeneous Bio- and Chemo-Catalysis for Dynamic Kinetic Resolution of (rac)-Benzoin

Rene Nieguth, Jeroen ten Dam, Annika Petrenz, Anand Ramanathan, Ulf Hanefeld, Marion B. Ansorge-Schumacher*

Enantiomerically pure acyloins are important building blocks for the synthesis of chiral fine chemicals and pharmaceuticals. Here, a highly efficient system for the enantiopure synthesis of benzoin was developed. The reaction system employed lipase TL from *Pseudomonas stutzeri* immobilized on Accurel MP1001 (Acc-LipTL) and Zr-TUD-1 (Si/Zr=25), an acidic mesoporous silicate, for dynamic kinetic resolution of racemic benzoin in one pot.

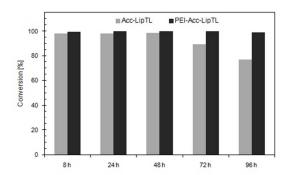

RSC Advances

RSCPublishing

ARTICLE

Combined Heterogeneous Bio- and Chemo-Catalysis for Dynamic Kinetic Resolution of *(rac)*-Benzoin

Cite this: DOI: 10.1039/x0xx00000x

R. Nieguth, a J. ten Dam, b A. Petrenz, c A. Ramanathan, b,d U. Hanefeld, b and M. B. Ansorge-Schumacher $^{a, c, *}$

Received ooth January 2012, Accepted ooth January 2012


DOI: 10.1039/x0xx00000x

www.rsc.org/

Dynamic kinetic resolution (DKR) of racemic starting material is a promising route to optically pure (*S*)-benzoin (2-hydroxy-1,2-di(phenyl)ethanone) and various symmetrical and unsymmetrical derivatives thereof. Here, this route was advanced towards technical scale synthesis using the basic (*rac*)-benzoin as model system. The reaction employed stereoselective transesterification of (*S*)-benzoin with lipase TL® from *Pseudomonas stutzeri* and racemization of (*R*)-benzoin with Metal-TUD-1, a metal-associated acidic meso-porous silicate, in pure organic solvent. Enzyme performance was improved by immobilization on Accurel MP1001 (yielding Acc-LipTL), and Zr-TUD-1 (Si/Zr=25) was identified as most effective racemization catalyst. Compatibility in solvent and temperature dependency enabled performance in only one pot. DKR in toluene at 50 °C yielded conversions above 98 % and an *ee* of >97 % in only five hours. Stability of Acc-LipTL was further improved with polyethylene imine and the reaction system was then reused in five cycles, retaining a conversion of >99 % and a product-*ee* of >98 %. On a semi-preparative scale, the isolated yield of enantiopure (*S*)-benzoin butyrate was >98 %. Thus, the system provides a good basis for synthesis of enantiopure benzoin, and potentially a broader range of aromatic α-hydroxy ketones.

Introduction

Enantiomerically pure acyloins (α -hydroxy ketones) provide important structural motifs for a number of fine chemicals and pharmaceuticals.^{1, 2, 3} Hence, various synthetic routes, chemoor biocatalytic, have been described to date.² They considerably differ in selectivity and yield, as well as in the accessible range of concrete structures (*i.e.* aliphatic, heterocyclic, aromatic, symmetrical, unsymmetrical, *R-/S*-stereochemistry, etc.) giving a portfolio of potentially interesting methods.

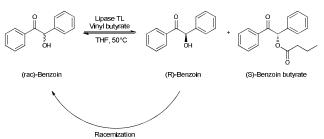

Scheme 1. Dynamic kinetic resolution of benzoin using vinyl butyrate as acyl donor and Lipase TL[®] as catalyst.

Dynamic kinetic resolution (DKR) of racemic starting material by combination of a biocatalysed kinetic resolution (KR) with *in situ* racemisation (RAC) of the undesired substrate

enantiomer (Scheme 1) has recently been described as a promising route to optically pure (S)-benzoin (2-hydroxy-1,2-di(phenyl)ethanone) and various symmetrical and unsymmetrical derivatives of this basic aromatic α -hydroxy ketone. ³⁻⁵

The method involves stereoselective transesterification of (rac)-benzoin with a lipase from Pseudomonas stutzeri (commercialised by Meito Sangyo Co., Japan, under the trade name of Lipase TL®, and immobilised through entrapment of the crude enzyme powder in a silicone matrix) and RAC with a homogeneous ruthenium based transition metal catalyst (Shyo's catalyst) and achieves substrate conversions above 90%. As product, (S)-configured butyrate esters with an enantiomeric excess above 99% are obtained, from which enantiopure (S)benzoin derivatives can easily be released through hydrolysis (e.g. using Lipase TL® under suitably adapted conditions). Despite this encouraging performance, however, the approach has not been transferred to synthetic application on a larger scale to date due to several unfavourable characteristics: 1. Reproducibility of catalytic efficiency between separate reaction batches is low. Most probably this is connected to the preparation of the biocatalyst which must lead to an uneven and uncontrollable distribution of the lipase within the particles and hence to widely varying catalytic performance. Additionally, sensitivity of the ruthenium catalyst for traces of molecular oxygen in the reaction set-up, and interference of acetaldehyde released from vinyl butyrate (i.e. the optimal acyl donor for benzoin esterification⁴) with the ruthenium catalyst⁶ could be an

ARTICLE Journal Name

RSC Advances

issue. 2. The ruthenium catalyst cannot be recycled, which increases both costs for reaction and costs for product workup. 3. Reaction conditions required for optimal performance and stability of bio- and chemo-catalyst (*e.g.* temperature) are hardly compatible resulting in low total turnover numbers and consequently large catalyst consumption. However, this specific item could recently be overcome by introduction of a novel ruthenium complex for racemization.⁷

This paper describes the advancement of DKR for technical scale hydroxy ketone synthesis with regard to reproducibility, catalyst recyclability and performance in one pot using DKR of (rac)-benzoin as model system. The study involved systematic development of a controllable and reproducible protocol for Lipase TL® immobilisation and introduction of a heterogeneous metal catalyst for racemization. Kinetic resolution and racemization of benzoin with these catalysts were characterised both separately and in a one-pot DKR. Optimisation was performed with regard to reaction medium and temperature. The synthetic potential of the approach was demonstrated on a semi-preparative scale.

Results and discussion

Page 3 of 10

Immobilisation of Lipase TL®.

For immobilisation of Lipase TL® (further annotated as LipTL) adsorption to the porous polypropylene resin Accurel MP1001 was selected. Leaching of enzyme during reaction must not be expected due to its insolubility in hydrophobic solvents making covalent attachment unnecessary.

Accurel is a highly hydrophobic material, for which beneficial effects on the catalytic behaviour of bound enzymes has been reported before. The obtained material had a size distribution of 400-1000 µm in diameter (Figure 1) and a specific surface of 35 m² (according to the BET method). The surface topology of individual particles, especially regarding pore size, was rather diverse. It can be assumed, however, that all microscopically visible pores are macroporous (*i.e.* displaying a diameter >500 nm) and are thus at least one to two orders of magnitudes larger than LipTL. Size differences should therefore be of only minor importance to the uptake of this enzyme.

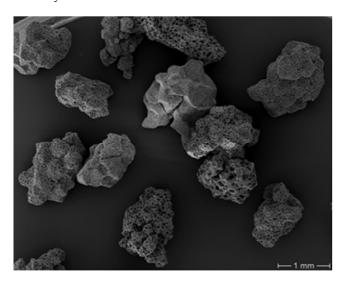


Figure 1. SEM-picture of Accurel MP 1001.

Enzyme immobilisation by adsorption is a spontaneous process running into a distinct thermodynamic equilibrium of bound and unbound protein. The position of equilibrium is influenced by many factors including carrier constitution and preparation conditions. A key role is played by the protein concentration in the immobilisation set-up. The amount of protein bound to the carrier is usually proportional to the available surface of the carrier until the binding capacity is exceeded, the protein aggregates, or multilayers are formed. Accordingly, optimum conditions for adsorption of LipTL on Accurel MP1001 were determined by introducing different concentrations of the crude preparation into the immobilisation process. Success was evaluated with regard to the specific catalytic activity of the resulting immobilisates in the transesterification of benzoin with vinyl butyrate using tetrahydrofuran (THF) as solvent.^{4, 10} The immobilised preparation is further denoted as Acc-LipTL.

The specific catalytic activity of Acc-LipTL increased with increasing concentrations of LipTL in the immobilisation process up to a steady value of 18.4 U $g_{Acc-LipTL}^{-1}$ correlating to a powder concentration of and above 60 mg_{LipTL} · $mL_{immobilisation}$ $medium^{-1}$ (Figure 2). Loading at this concentration was determined as 15.4 $mg_{Protein}$ · $g_{Accurel}$ - g_{A

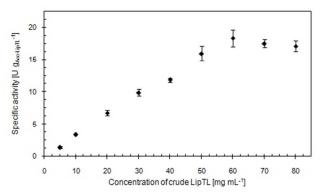


Figure 2. Influence of LipTL concentration in the immobilisation set-up (10 mmol·L⁻¹ KP_i buffer, pH 7.0) on the resulting specific activity of immobilised Acc-LipTL (carrier concentration fixed at 50 mg·mL⁻¹).

An increase in the specific catalytic activity of LipTL through immobilisation (by factor 2.2) had also been observed by Hoyos et al. 5 As an explanation the enhanced transfer of the hydrophobic substrates and products through the also hydrophobic silicone matrix, and a stabilisation of the catalytic active conformation of LipTL (generally recognised as hyperactivation or interfacial activation) were suggested. This active conformation usually describes a state where an amphipathic peptide chain (lid) at the active site of the enzyme is open due to the interaction of its hydrophobic part with a hydrophobic interface or surface, 11 and it has only lately been reported that LipTL might contain even two such lids. 12 Both explanations could equally apply to the behaviour of LipTL on Accurel MP1001 due to the distinct hydrophobicity of this material. In addition - or alternatively -, a selective binding of LipTL to the carrier could occur which would result in a purification of the enzyme. According to Maraite et al. 12, commercial LipTL contains an assortment of side proteins that

RSC Advances Page 4 of 10

Journal Name ARTICLE

might (at least partly) have a significantly lower affinity to the hydrophobic support than the lipase itself. Even simpler, the activity increase on Accurel MP1001 could be connected with the more even distribution of the enzyme, and therefore better accessibility, on the carrier compared to suspended (and usually aggregated) solid enzyme in pure organic solvents. Overall, the results strongly support the suitability of Accurel MP1001 as a carrier for LipTL.

On the assumption that the observed maximum specific activity of Acc-LipTL at a concentration of 60 mg_{LipTL}·mL_{immobilisation medium}-1 correlated to the arrival at the maximum binding capacity and might therefore prohibit detection of further effects on activity, further experiments on the optimisation of the immobilisation process were performed at a constant concentration of 30 mg_{LipTL}·mL_{immobilization medium}-1. Buffer (KP_i) concentration and pH were varied between 10 mmol·L⁻¹ and 400 mmol·L⁻¹ and around the isoelectric point of LipTL (*i.e.* 6.6) to pH 6.2, pH 6.6 and pH 7.0, respectively.

Optimum conditions with regard to the specific catalytic activity of Acc-LipTL were found at a buffer concentration of 200 mmol·L⁻¹ and pH 6.2, with the buffer concentration as the decisive parameter (Figure 3). The maximum specific activity was 24.7 U·g_{Acc-LipTL}⁻¹. At a loading of 17.8 mg_{Protein}·g_{Accurel}⁻¹, this corresponded to a protein related specific activity of 1,4 U·g_{Protein}⁻¹, which was an increase by factor 4.1 compared to crude LipTL and was almost two-fold better than the effect of silicone entrapment as described by Hoyos *et al.*⁵

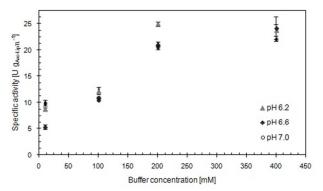


Figure 3. Influence of KP_i buffer concentration and pH in the immobilisation set-up on the resulting specific activity of immobilised Acc-LipTL (LipTL concentration fixed at $30~mg_{LipTL}\cdot mL_{immobilisation~medium}^{-1}$ and carrier concentration at $50~mg\cdot mL^{-1}$).

The findings on buffer and pH effects are in good agreement with the assumption that the adsorptive binding of proteins to the nonionic Accurel MP1001 is predominantly promoted by hydrophobic interactions: changes of pH have only minor effects on such binding forces, while phosphate anions comprising the buffer are kosmotropic in nature and are therefore strengthening them. The same effects are exploited in hydrophobic interaction chromatography, where high ionic strengths are used to selectively bind hydrophobic proteins.¹³

Transfer of these optimum conditions to LipTL immobilisation at an initial powder concentration of 60 mg_LipTL mL_immobilisation $_{\rm medium}^{-1}$ resulted in a minor improvement of the specific catalytic activity to 28.2 U·g_Acc_LipTL 1, which was in perfect agreement with the initial assumption on already saturated loading at this protein concentration. As the poor additional benefit did not justify

consumption of the double amount of the valuable enzyme, a LipTL concentration of 30 $mg_{\text{LipTL}} \cdot mL_{\text{immobilisation medium}}^{-1}$ was established in the final immobilisation protocol.

KR of (rac)-benzoin

Acc-LipTL was subjected to KR of (*rac*)-benzoin using dried THF, 2-MeTHF and toluene, respectively, as solvents. The selection was based on the reported suitability of THF and its environmentally benign derivative 2-methyl tetrahydrofuran (2-MeTHF) for kinetic resolution of benzoin,^{4, 10, 14} and of toluene for racemization.¹⁵ At room temperature (21.5 °C), Acc-LipTL displayed good activity in all three solvents (Table 1, column 3). The time to reach maximum conversion (*i.e.* 50 %), however, was considerably shorter in 2-MeTHF and toluene (2.5 h) than in THF (>4 h) (Table 1, column 4). The half-life of Acc-LipTL under process conditions (calculated from the decrease of conversion after reaching steady-state in a continuous reaction set-up) was about 1.6-fold and 2.9-fold higher in 2-MeTHF than in toluene and THF, respectively.

Table 1. Specific activity of Acc-LipTL in the KR of benzoin using different (dry) solvents at room temperature or 50 °C, respectively (catalyst concentration fixed at 20 mg_{Acc-LipTL} mL·1; 47 mmol·L⁻¹ (*rac*)-benzoin).

Solvent	Temp	Specific activity	Time to	ee a)
	[°C]	[U·g _{AcclipTL}]	max. conv. (50 %) [h]	[%]
THF	21.5	13.0	4	>99
	50	36	3.5	>99
2-MeTHF	21.5	20.7	2.5	>99
	50	47.8	1.5	>99
Toluene	21.5	15.2	2.5	>99
	50	62	1.5	>99

a) ee of (S)-benzoin butyrate

Similar results were obtained at 50 °C, which is the temperature preferable for running the racemization catalyst. Interestingly, the specific activity of Acc-LipTL in toluene now exceeded the activity in 2-Me-THF, while the time to obtain full conversion was still similar. The time to reach full conversion in THF changed only slightly compared to the reaction at room temperature. Both findings can easily be explained by a lower stability of Acc-LipTL in toluene and THF, respectively, than in 2-MeTHF confirming the observations on process stability described above. Notably, in both 2-Me-THF and toluene KR can obviously be run efficiently at 50 °C.

Racemization of (R)-benzoin

Apart from the homogeneous Shvo's catalyst, several heterogeneous catalysts display activity on secondary alcohols including transition metals supported on carbon, hydroxyapatite or alumina, acidic resins, vanadium catalysts and zeolites. ^{16, 17} As demonstrated in earlier studies, commercial ion-exchangers

Page 5 of 10 **ARTICLE** Journal Name

RSC Advances

exert a detrimental effect on enzyme activity, 18 and are therefore not suitable for a one pot DKR as targeted in this study. Heterogeneous (semi-) precious metal catalysts, on the other hand, usually suffer from high costs and leaching of the active species, while Zeolites have only small pore sizes limiting their application to small substrates. Both disadvantages, however, can be overcome by use of mesoporous material: Framework incorporation of active metals suppresses leaching and large pores allow full accessibility even for large substrates. 19, 20 TUD-1 is a mesoporous material with a sponge-like structure and threedimensional pores.²¹ Its environmentally benign synthesis allows for the straightforward introduction of a large range of metals into the framework. High stability and recyclability has been demonstrated in many different reactions, in particular in the Meerwein-Ponndorf-Verley reduction and the Oppenauer oxidation. 19, 21-23 Moreover, its induced acidic sites make it ideal for the generation of carbenium ions, intermediates in the racemization of benzylic alcohols, while side reactions often observed with commercially available acid resins do not occur. Accordingly, TUD-1 catalysts were tested for racemization of (R)-benzoin. As incorporated metals, aluminium, ²⁴, zirconium, ^{15, 26} and tungsten, ²⁷ respectively, were involved.

Based on the findings on KR performance with Acc-LipTL (see previous section) and on the study of Ramanathan et al., 15 toluene was chosen as the solvent for racemization. The racemization success was measured in terms of enantiomeric excess (ee), for which in this case a value as small as possible was targeted. Results are summarized in Table 2.

Table 2. Racemization of (R)-benzoin with TUD-1 catalysts incorporating different metals at varying concentration; the reaction was performed in toluene at 50 °C using 20 mg of catalyst per batch.

Entry	Catalyst	Time [h]	ee [%]
1	TUD-1	20	93.8
2	Zr-TUD-1 (Si/Zr=25)	20	1.3
3	Al-TUD-1 (Si/Al=4)	20	0.2
4	Al-TUD-1 (Si/Al=25)	20	23.2
5	W-TUD-1 (Si/W=10)	20	65.7
6	W-TUD-1 (Si/W=20)	20	43.9
7	W-TUD-1 (Si/W=30)	20	63.9
8	W-TUD-1 (Si/W=40)	20	73.7
9	W-TUD-1 (Si/W=50)	20	71.7
10	Zr-TUD-1 (Si/Zr=25)	4	4.4
11	Al-TUD-1 (Si/Al=4)	4	42.8

It was observed that purely siliceous TUD-1 (i.e. without any metal incorporated) was already able to catalyse the racemization of (R)-benzoin, although not very efficiently. An ee of 93.8 % was obtained after 20 h at 50 °C. Under the same conditions, introduction of tungsten to TUD-1 (W-TUD-1) yielded a maximum ee of 43.9 % at a ratio of Si/W=20. Increases in the metal content initially

enhanced the reaction rate, while after surpassing a maximum racemization activity, high loadings of tungsten were less efficient. As tungsten provides the acidic reaction site for racemization, this behaviour is a reaction to the actual availability of reactive centers. It increases with incorporation of tungsten until the formation of crystalline tungsten oxide species with a reduced surface area and therefore lower accessibility of the acidic metal occurs.


Excellent racemization results were obtained with aluminum and zirconium as incorporated metals. After 20 h at 50 °C both Zr-TUD-1 (Si/Zr=25) and Al-TUD-1 (Si/Al=4) had completely racemised (R)-benzoin. After a reaction time of only four hours (which is in the time range of KR with Acc-LipTL in toluene, (see previous section) Zr-TUD-1 (Si/Zr=25) reduced the ee to 4.4 %, while Al-TUD-1 (Si/Al=4) managed a final ee of 42.8 %. Thus, Zr-TUD-1 demonstrated a superior racemization activity, which is most likely due to the purely Lewis acidic nature of zirconium in the framework of TUD-1, 19 contrasting the mixed Lewis and Brønsted acid character imparted by tungsten and aluminum. 15, 22, 25 Importantly. Zr-TUD-1 showed no racemization activity with (R)-benzoin butyrate (within two hours) even at high temperature (70°C) and thus ensures that the enantiopurity of the KR product cannot be affected.

For investigation of temperature effects on the racemization efficiency both Zr-TUD-1 (Si/Zr=25) and Al-TUD-1 (Si/Al=4) were subjected to higher reaction temperatures (50, 70 and 90 °C). As expected from the Arrhenius relation, the racemization rate increased with increasing temperature in both cases (Figure 4). With Zr-TUD-1 (Si/Zr=25) complete racemization was achieved within 90 minutes at 70 °C and only 30 minutes at 90 °C. With Al-TUD-1 (Si/Al=4) considerably longer reaction times were required. The minimum was 90 minutes at a temperature of 90 °C. Notably, only small amounts of benzil, the dicarbonyl analogue of benzoin, were detected in all set-ups indicating that dehydrogenation, which had been described in connection with acidic racemization of hydroxyl compounds before, $^{17,\,18,\,28}$ plays a minor role in the racemization of benzoin with the selected TUD-1 catalysts.

The tendency of Zr-TUD-1 and Al-TUD-1 to catalyze unspecific transesterification of benzoin in the final reaction mixture as a likely side reaction^{17, 18, 28} was investigated by incubation of a mixture of catalyst, (rac)-benzoin and vinyl butyrate in toluene at different temperatures. Under all conditions strong transesterification activity was observed with Al-TUD-1 (Figure 5), yielding benzoin ester amounts comparable to the enzymatic reaction. Due to the fully racemic nature of the ester, this would diminish the product-ee in a onepot DKR considerably. In contrast, Zr-TUD-1 revealed strong transesterification activity only at high temperature (90 °C). Hardly any benzoin ester was detected at 50 °C or 70 °C. Thus, Zr-TUD-1 makes a selective racemization catalyst up to a temperature of at least 70 °C. Most probably, this can again be explained by the Lewis acidic character of the catalyst, which avoids initiation of transesterification via Brønstedt protonation of the carbonyl group in the acyl donor (which is then attacked by the nucleophilic alcohol).²⁹

Journal Name RSC Advances Page 6 of 10

ARTICLE

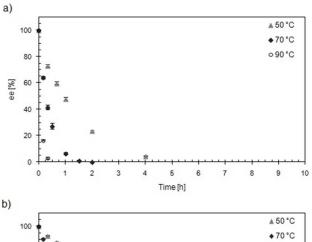

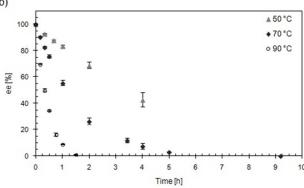


Figure 4. Racemization of (*R*)-benzoin with a) Zr-TUD-1 (Si/Zr=25) and b) Al-TUD-1 (Si/Al=4) in toluene at different temperatures (the catalyst concentration was fixed at 40 mg·mL⁻¹; the reaction was performed in 500 μL solvent with 94 mM (*R*)-benzoin).

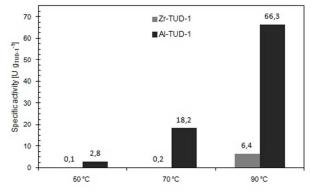


Figure 5. Specific activity of Al-TUD-1 (Si/Al=4) and Zr-TUD-1 (Si/Zr=25) in the transesterification of vinyl butyrate and benzoin in toluene at different temperatures (catalyst concentration fixed at 40 mg_{TUD-1}·mL⁻¹; 500 μL solvent with 94 mM (*rac*)-benzoin as reaction medium).

DKR of (rac)-benzoin

DKR of (rac)-benzoin was performed in one pot using a combination of Acc-LipTL and metal-TUD-1 as catalysts and vinyl butyrate as acyl donor. In contrast to the reaction set-up of Hoyos et al., 4 use of this most efficient acyl donor was possible, because inactivation of metal-TUD-1 by the emerging volatile acetaldehyde, as observed with Shvo's catalyst, was not to be

expected. For optimisation the reaction was investigated using THF, 2-MeTHF and toluene, respectively, as solvents and at temperatures up to $90~^{\circ}\text{C}$.

Excellent results were obtained with Acc-LipTL and Zr-TUD-1 (Si/Zr=25) in toluene and equally in 2-MeTHF (Table 3). In toluene 98.4 % of the deployed (*rac*)-benzoin was converted within 5 h yielding a product-*ee* of 98.5 %. Within the same time range, conversion was only slightly lower in 2-MeTHF (96.8 %) yielding a still remarkable product-*ee* of 97 %. Interestingly, the situation was controversial when Al-TUD-1 (Si/Al=4) was used as racemization catalyst, which can most probably be explained by the lower racemization activity of Al-TUD-1 in 2-MeTHF compared to toluene (Table 3) entailing an also lower unspecific transesterification activity.

In THF, the DKR was ineffective with both racemization catalysts yielding lower (Al-TUD-1) or only slightly higher (Zr-TUD-1) conversion than theoretically possible in KR (*i.e.* 50 %). This was surprising considering the good results of separate (*R*)-benzoin racemization in this solvent (see Table 3). The behavior might be connected with side activities of the acidic catalysts under certain conditions (*e.g.* catalysis of polymerisation)^{14, 30} affecting their racemization activity.

Importantly, it becomes obvious from the performances of the separate and combined catalysts (Tables 2 and 3) that prediction of the best conditions for one pot DKR can hardly be based on the separate reactions. While Al-TUD-1 (Si/Al=4) in 2-MeTHF leads to faster racemization of benzoin than Zr-TUD-1 (Si/Zr=25), Zr-TUD-1 is the catalyst of choice for the DKR. Toluene turns out to be the best solvent (with 2-MeTHF as a close second) even though it is only second choice for the KR on its own. This highlights the complexity of combination reactions with two types of catalyst, here heterogeneous and biological, as multi-parameter problems.³¹

Table 3. Racemization performance of Al-TUD-1 (Si/Al=4) and Zr-TUD-1 (Si/Zr=25) and results of DKR with both metal catalysts and Acc-LipTL in different solvents at 50 °C (catalyst concentration fixed at 40 $\rm mg_{TUD-1} \cdot mL^{-1}$ and 20 $\rm mg_{Acc-LipTL} \cdot mL^{-1}$; 500 $\rm \mu L$ solvent with 94 mM (*rac*)-benzoin as reaction medium)

Solvent	Rac. catalyst	ee after rac [%] ^{a)}	Conv. DKR [%] ^{b)}	ee DKR [%] ^{b)}
THF	Al-TUD-1	11.9	25.1 ^[c]	84.2
	Zr-TUD-1	23.4	53.5 ^[c]	99.6
2-MeTHF	Al-TUD-1	7.7	85.9	96.6
	Zr-TUD-1	11.4	96.8	97
Toluene	Al-TUD-1	0.2	93.2	83.3
	Zr-TUD-1	1.3	98.4	98.5

a) ee of (R)-benzoin, 20 h at 50 °C; b) 5 h at 50 °C, c) ee of (S)-benzoin butyrate, increased side product formation indicating side activities of the catalyst(s).

Considering that both KR and racemization, but also unspecific transesterification and biocatalyst inactivation,

Page 7 of 10 **ARTICLE** Journal Name

RSC Advances

proceed faster at elevated temperature, DKR of benzoin using Acc-LipTL and Zr-TUD-1 (Si/Zr=25) in toluene was studied at 50 °C, 70 °C and 90 °C (Figure 6). At 50 °C, the conversion was over 98 % after 5 h with an ee of 98.5 %. The reaction time for reaching >98 % conversion was reduced to 3.5-4 h when the DKR was performed at 70 °C, while a still very good productee of 97.6 % was obtained. The minor decrease in ee can certainly be explained by the small unspecific transesterification activity of Zr-TUD-1 at this temperature (see previous section). In agreement with this assumption, the ee dropped to 65.2 % at a reaction temperature of 90 °C, where the unspecific transesterification activity of Zr-TUD-1 is considerable. Notably, full conversion was still obtained at this temperature (within 1.5 h) demonstrating a remarkable thermostability of the immobilized biocatalyst under the applied conditions.

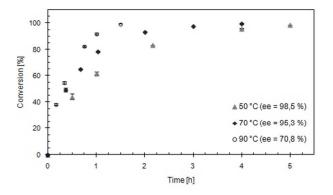


Figure 6. DKR of (rac)-benzoin catalyzed by Acc-LipTL and Zr-TUD-1 (Si/Zr=25) in toluene at different temperatures.

In view of application in technical synthesis benefitting from repetitive (or continuous) use of the catalysts, 31 recyclability of Acc-LipTL and Zr-TUD-1 in DKR was investigated. Repeated batchcycles were performed in toluene and 2-MeTHF, respectively, at 50 °C. After each cycle the catalysts were separated by filtration and washed with the respective solvent until no residual substrates or product were detectable in HPLC analysis. In comparison of the two solvent systems the reaction time was chosen in a way that both reactions were stopped when full conversion (>99%) was first accomplished in one of the reactions. The maximum reaction time per batch was 24 h.

In 2-MeTHF full conversion of (rac)-benzoin (>99 %) was obtained over three batches (Figure 7) with a runtime of 8 h, 16 h and 24 h, respectively. In the same time intervals DKR in toluene achieved >99 % in the first, 96 % in the second and only 84 % in the third cycle. Product-ee was >97 % in both solvents throughout all experiments. The increasing runtimes per cycle required to obtain full conversion in at least one solvent as well as the lower conversion in toluene than in 2-MeTHF within comparable time intervals most probably indicate catalyst deactivation, with a stronger effect exerted by toluene. In principal, this deactivation could concern Acc-LipTL as well as Zr-TUD-1. However, considering that an excellent reusability has been reported for Zr-TUD-1 in the cyclisation of raccitronellal, 15 deactivation of the enzyme catalyst is more likely. This also agrees with the solvent effects on the activity and process stability of Acc-LipTL observed in separate KR (see Table 1).

In fact, stability of the reaction system on repetitive use in 2-MeTHF was considerably enhanced (Figure 8) when the biocatalyst, Acc-LipTL, was stabilized by incubation in a PEI-buffer solution prior to drying as suggested by Guisan et al. 32 While in DKR with untreated Acc-LipTL, conversion decreased to 89 % in the fourth and 78 % in the fifth cycle (each cycle with a runtime of 24 h), use of Acc-LipTL treated with PEI enabled full conversion (>99 %) in all cycles. The product-ee remained at >98 % and was therefore unaffected by the treatment.

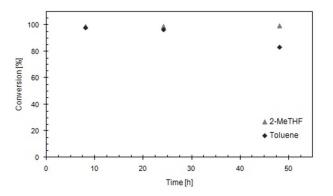


Figure 7. Repeated DKR of (rac)-benzoin with Acc-LipTL and Zr-TUD-1 (Si/Zr=25) in toluene or 2-MeTHF, respectively, at 50 °C. Each data point is the endpoint of a cycle over accumulated time. Reactions were stopped when full conversion was first accomplished in one of the solvents.

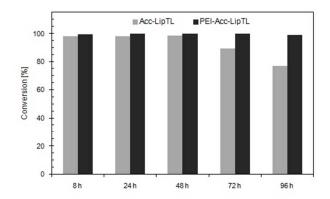


Figure 8. Repeated DKR of (rac)-benzoin with Zr-TUD-1 (Si/Zr=25) and untreated Acc-LipTL or PEI-Acc-LipTL, respectively, in 2-MeTHF at 50 °C. Each data point is the endpoint of a cycle over accumulated time.

Finally, the actual practicability of the process for synthesis was demonstrated by performing the DKR on a semipreparative scale using 150 mg racemic benzoin as substrate. The reaction proceeded as smoothly as in small scale (data not shown), reaching 92% conversion within 5 hours and full

RSC Advances Page 8 of 10

conversion within less than 20 hours. The product was a colourless oil consisting of enantiopure (ee > 98%) (S)-benzoin butyrate (1 H-NMR (400 MHz, CDCl₃): 7.92 (m, 2H; Ar-H), 7.55-7.3 (m, 8H; Ar-H), 6.85 (s, 1H; CHO), 2.51-2.39 (m, 2H; CH₂), 1.74-1.60 (m, 2H; CH₂), 0.98-0.90 (m, 3H; CH₃); consult Figure S1 in the supplementary material for the spectrum). The isolated yield after removal of catalysts and solvent was 196 mg corresponding to more than 98%. Thus, the performance of the proposed one-pot system is very promising with regard to synthetic application.

Experimental

Journal Name

Materials

Lipase TL from *P. stutzeri* was a gift from Meito & Sangyo Co., Ltd. (Tokyo, Japan). Accurel MP1001 was obtained from Membrana (Wuppertal, Germany). TUD-1 catalysts were activated *via* calcination in the presence of air at up to 600 °C at a temperature ramp of 1 K min⁻¹ and subsequent heating for 10 h at 600 °C. After cooling down to 100 °C the catalysts were stored at 100 °C until use. All chemicals and liquid substrates were purchased from Aldrich (Steinheim, Germany), VWR (Darmstadt, Germany) or Carl-Roth (Karlsruhe, Germany) and used as received. All solvents were dried over activated molecular sieves before use.

Reaction analysis

Conversion and enantiomeric excess (*ee*) were determined *via* HPLC analysis using a Daicel Chiralpak IA column at a flow of 2,0 mL·min⁻¹ of *n*-hexane/isopropyl alcohol (90/10) at 40 °C. Typical retention times were 2.9 min for (*R*)-benzoin butyrate, 3.3 min for (*S*)-benzoin butyrate, 5.8 min for (*R*)-benzoin and 6.6 min for (*S*)-benzoin. An exemplary spectrum is given in the supplementary material (Figure S1).

Immobilization of lipase TL

Lipase TL powder was stirred in KPi buffer at room temperature until agglomerates were no more visible. Undissolved material was separated by centrifugation at 5,000 rpm for 10 minutes. 500 mg Accurel MP1001 were placed in 3.75 mL ethanol (abs.) for 30 minutes, then 10 mL of lipase solution was directly added. The sealed vessel was placed on an orbital shaker at 340 rpm and 40 °C for 4 h. The immobilisates were afterwards filtered from the solution and washed 2 times with 10 mL immobilization buffer. After final vacuum filtration the Acc-LipTL particles were dried *via* storing over silica gel at reduced pressure and room temperature until use.

Kinetic resolution (KR)

Typically 20 mg·mL⁻¹ (94 mM) *(rac)*-benzoin was dissolved in dry organic solvent (usually THF). 10 mg of lipase were added to 1 mL of the benzoin solution and the mixture was incubated on a thermoshaker at 1,200 rpm and room temperature. After 10 min. KR was started by addition of 6 eq. (related to benzoin) of vinyl butyrate. For sample analysis 10 μ L reaction medium were dissolved in 990 μ L isopropyl alcohol. If crude lipase powder was used, the diluted samples were centrifugated and the supernatant was analyzed. Conversion and enantiomeric excess were determined *via* HPLC analysis.

Racemization of (R)-benzoin

20 mg metal-TUD-1 catalyst were loaded in a dried Schlenk flask under nitrogen atmosphere. (R)-benzoin was dissolved in toluene at a concentration of 20 mg·mL⁻¹; slight heating was required for complete dissolvation. Racemization was started by adding 500 μ L of the substrate solution to the metal-TUD-1 catalysts in the Schlenk flask. The reaction vessel was immediately placed in a temperated oil bath (temperature depending on the reaction temperature of following racemization reactions) and mixed with a magnetic stir bar. For sample analysis 10 μ L reaction medium.were taken under nitrogen counter flow in appropriate time intervals and were dissolved in 990 μ L isopropyl alcohol. Enantiomeric excess was determined via HPLC analysis.

Dynamic kinetic resolution (DKR)

For characterisation and optimisation, 10 mg Acc-LipTL and 20 mg Metal-TUD-1 (Si/Zr=25) were loaded in a dried Schlenk flask under nitrogen atmosphere. Benzoin was dissolved in toluene at a concentration of 20 mg·mL⁻¹; slight heating was required for complete dissolvation. 500 µL of the substrate solution were added to the lipase and metal-TUD-1 in the Schlenk-flask and the mixture was incubated for 10 minutes. DKR was started by addition of 6 eq. (related to benzoin) of vinyl butyrate and the reaction vessel was immediately placed in a temperature controlled oil bath (temperature depending on the desired reaction temperature) and mixed with a magnetic stir bar. For sample analysis, 10 µL reaction medium.were taken under nitrogen counter flow in appropriate time intervals and were dissolved in 990 µL isopropyl alcohol. Conversion and enantiomeric excess were determined via HPLC analysis. For recycling experiments the catalysts (Acc-LipTL and Metal-TUD-1) were separated from the reaction mixture by filtration and washed two times with the solvent providing the reaction medium. After final filtration new substrate solution was added and the reaction was restarted by adding vinyl butyrate under nitrogen atmosphere. The runtime of reaction cycles was adjusted for first reaching a conversion of >98 % in one of the solvents. The maximum reaction time was limited to 24 h. For scale-up, the reaction volume was increased to 7.5 mL toluene, using. 300 mg Zr-TUD-1 (Si/Zr=25), 150 mg Acc-LipTL, 150 mg racemic benzoin and 400 mg vinyl butyrate. The reaction was performed under stirring at 50 °C. Samples were taken and defined time intervals and reaction progress was followed via HPLC analysis. After reaching full conversion the catalysts were filtered off and the solvent was removed under reduced pressure.

Determination of LipTL stability

A sealed vessel with a volume of 6 mL was continuously operated by using a HPLC pump at a flow rate of 0,5 mL·min⁻¹. The benzoin solution (10 mg·mL⁻¹ (47 mM) in the given solvent (THF as standard)) with 3 eq. vinyl butyrate was introduced through a pipe and left the reactor by a bleeder pipe. The reaction medium was vigorously mixed with a magnetic stir bar. 100 mg of Acc-LipTL was loaded in the reactor and the reaction was performed until a steady state was reached. For sample analysis 10 μL reaction medium were taken from the outlet stream and dissolved in 990 μL isopropyl alcohol. Conversion and enantiomeric excess were determined *via* HPLC analysis. From the decrease of the conversion (never exceeded 10 %) over time the half life of Acc-Lip TL could be determined.

ARTICLE

Modification of Acc-LipTL

100 mg Acc-LipTL were incubated in 7,5 mL ethanol (abs.) for 30 minutes. 2 mL of polyethylene imine (PEI)-solution (1 % in 200 mmol·L⁻¹ KPi) were added to the mixture and the sealed vessel was incubated on an orbital shaker for 1 h at 340 rpm and room temperature. The particles were separated by filtration, washed two times with KPi buffer and dried *via* storing over silica gel at reduced pressure and room temperature until use.

Conclusions

By appropriate preparation and choice of biocatalyst and chemocatalyst, respectively, dynamic kinetic resolution of (rac)-benzoin has been considerably advanced towards preparative scale synthesis. Particularly beneficial were the targeted heterogenization of LipTL through adsorption on Accurel MP1001 and the implementation of heterogeneous Sibased Zr-TUD-1 as racemization catalyst. Both promoted reproducibility of application and recycling of catalysts, and in combination yielded full conversion (> 99 %) at very high product-ee (>98 %) in less than 20 hours. Compatibility in solvent and temperature dependency enabled performance in only one pot. The application range of the reaction system will have to be elucidated in further studies, in view of the documented broad substrate range of LipTL,3-5 however, accessibility of various α-hydroxy ketones via this route can actually be envisaged.

Notes and references

- ^a Lehrstuhl für Technische Chemie/Enzymtechnologie, Institut für Chemie, Technische Universität Berlin, 10623 Berlin, Germany.
- ^b Gebouw voor Scheikunde, Biokatalyse, Afdeling Biotechnologie, Technische Universiteit Delft, Julianalaan 136, 2628 BL Delft, The Netherlands.
- ^c Professur für Molekulare Biotechnologie, Institut für Mikrobiologie, Technische Universität Dresden, 01062 Dresden, Germany, Tel: (+)49 351 46339518; Fax: (+)49 351 46339520, Email: marion.ansorge@tudresden.de.
- ^d Center for Environmentally Beneficial Catalysis, The University of Kansas, Lawrence, Kansas 66047, United States.
- Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/
- D. Enders and U. Kallfass, Angew. Chem. Int. Ed., 2002, 41, 1743; Y. Tachibana, N. Kihara and T. Takata, J. Am. Chem. Soc., 2004, 126, 3438; S. K. Alamsetti, P. Muthupandi and G. Sekar, Chem. Eur. J., 2009, 15, 5424; P. Muthupandi, S. K. Alamsetti and G. Sekar, Chem. Comm., 2009, 3288; P. Hoyos, M. A. Quezada, J. V. Sinisterra and A. R. Alcántara, J. Mol. Catal. B.: Enzymatic, 2011, 72, 20; T. Soeta, Y. Tabatake, K. Inomata and Y. Ukaji, Tetrahedron, 2012, 68, 894.
- P. Hoyos, J. V. Sinisterra, F. Molinari, A. R. Alcantara and P. Dominguez-de-Maria, Acc. Chem. Res., 2010, 43, 288.
- P. Hoyos, V. Pace, J. V. Sinisterra and A. R. Alcántara, *Tetrahedron*, 2011, 67, 7321.

 P. Hoyos, M. Hernandez, J. V. Sinisterra and A. R. Alcántara, J. Org. Chem., 2006, 71, 7632.

Journal Name

- P. Hoyos, A. Buthe, M. B. Ansorge-Schumacher, J. V. Sinisterra and A. R. Alcántara, J. Mol. Catal. B.: Enzymatic, 2008, 52-53, 133
- O. Pamies and J. E. Bäckvall, Curr. Opin. Biotechnol., 2003, 52-53, 133.
- S. Agrawal, E. Martínez-Castro, R. Marcos and B. Martín-Matute, Org. Lett., 2014, DOI: 10.1021/ol500764q.
- M. Persson, I. Mladenoska, E. Wehtje and P. Adlercreutz, Enzyme Microb. Technol., 2002, 31, 833;A. Salis, E. Sanjust, V. Solinas and M. Monduzzi, J. Mol. Catal. B.: Enzymatic, 2003, 24-25, 75;P. Torres, D. Reyes-Duarte, N. Lopez-Cortes, M. Ferrer, A. Ballesteros and F. J. Plou, Proc. Biochem., 2008, 43, 145.
- B. Al-Duri and Y. P. Yong, *Biochem. Eng. J.*, 2000, 4, 207;L. L. Cao, *Carrier-bound immobilized enzymes.*, Wiley-VCH, Weinheim, 2005;U. Hanefeld, L. Gardossi and E. Magner, *Chem. Soc. Rev.*, 2009, 38, 453.
- Y. Aoyagi, N. Agata, N. Shibata, M. Horiguchia and R. M. Williams, *Tetrahedron Lett.*, 2000, 41, 10159;Y. Aoyagi, A. Iijima and R. M. Williams, *J. Org. Chem.*, 2001, 66, 8010.
- 11. J. M. Palomo, G. Munoz, G. Fernandez-Lorente, C. Mateo, R. Fernandez-Lafuente and J. M. Guisan, *J. Mol. Catal. B.: Enzymatic*, 2002, **19**, 279.
- A. Maraite, P. Hoyos, J. D. Carbeillera, A. C. Cabrera, M. B. Ansorge-Schumacher and A. R. Alcántara, *J. Mol. Catal. B.: Enzymatic*, 2013, 87, 88.
- M. M. Diogo, S. Silva, J. M. S. Cabral and J. A. Queiroz, J. Chromatogr. A, 1999, 849, 413; A. C. Dias-Cabral, A. S. Ferreira, J. Phillips, J. A. Queiroz and N. G. Pinto, Biomed. Chromatogr., 2005, 19, 606.
- V. Pace, P. Hoyos, L. Castoldi, P. Dominguez-de-María and A. R. Alcántara, *ChemSusChem*, 2012, 5, 1369.
- 15. A. Ramanathan, M. C. C. Villalobos, C. Kwakernaak, S. Telalovic and U. Hanefeld, *Chem. Eur. J.*, 2008, **14**, 961.
- S. Wuyts, D. E. d. Vos, F. Verpoort, D. Depla, R. d. Gryse and P. A. Jacobs, J. Catal., 2003, 219, 417; W. H. Kim, R. Karvembu and J. Park, Bull. Korean Chem. Soc., 2004, 25, 931; A. Zsigmond, A. Kecskemeti, K. Bogar, F. Notheisz and E. Mernyak, Catal. Comm., 2005, 6, 520; A. Berkessel, M. L. Sebastian-Ibarz and T. N. Muller, Angew. Chem. Int. Ed., 2006, 45, 6567; S. Wuyts, J. Wahlen, P. A. Jacobs and D. E. d. Vos, Green Chem., 2007, 9, 1104; L. F. A. Costa, F. Lemos, F. R. Ribeiro and J. M. S. Cabral, Catal. Today, 2008, 133, 625; A. Parvulescu, J. Janssens, J. Vanderleyden and D. E. d. Vos, Top. Catal., 2010, 53, 931; Y. M. Cheng, G. Xu, J. P. Wu, C. S. Zhang and L. R. Yang, Tetrahedron Lett., 2010, 51, 2366; Y. M. Cheng, G. Xu, J. P. Wu and L. R. Yang, Chinese J. Org. Chem., 2010, 30, 1695.
- Y. Z. Zhu, K. L. Fow, G. K. Chuah and S. Jaenicke, *Chem. Eur. J.*, 2007, 13, 541.
- P. Odman, L. A. Wessjohann and U. T. Bornscheuer, *J. Org. Chem.*, 2005, 70, 9551.
- A. Ramanathan, D. Klomp, J. A. Peters and U. Hanefeld, *J. Mol. Catal. A: Chem.*, 2006, 260, 62.

20. Y. Wan and D. Y. Zhao, Chem. Rev., 2007, 107, 2821.

Journal Name

- S. Telalovic, A. Ramanathan, G. Mul and U. Hanefeld, *J. Mater. Chem.*, 2010, 20, 642.
- 22. S. Telalovic, J. F. Ng, R. Maheswari, A. Ramanathan, G. K. Chuah and U. Hanefeld, *Chem. Comm.*, 2008, 4631.
- S. Telalovic, A. Ramanathan, J. F. Ng, R. Maheswari, C. Kwakernaak, F. Soulimani, H. C. Brouwer, G. K. Chuah, B. M. Weckhuysen and U. Hanefeld, *Chem. Eur. J.*, 2011, 17, 2077.
- C. Simons, U. Hanefeld, I. W. C. E. Arends, R. A. Sheldon and T. Maschmeyer, *Chem. Eur. J.*, 2004, 10, 5829;S. Telalovic, S. K. Karmee, A. Ramanathan and U. Hanefeld, *J. Mol. Catal. A: Chem.*, 2013, 368, 88.
- A. Ramanathan, R. Maheswari and U. Hanefeld, *J. Catal.*, 2006, 242, 82.
- M. P. Pachamuthu, V. V. Srinivasan, R. Maheswari, K. Shanthi and A. Ramanathan, Appl. Catal. A: General, 2013, 462, 143.
- J. ten-Dam, D. Badloe, A. Ramanathan, K. Djanashvili, F. Kapteijn and U. Hanefeld, Appl. Catal. A: General, 2013, 468, 150.
- 28. S. Wuyts, K. de-Temmermann, D. E. d. Vos and P. A. Jacobs, *Chem. Eur. J.*, 2004, **11**, 386.
- U. Schuchardt, R. Sercheli and R. M. Vargas, J. Brazilian Chem. Soc., 1998, 9, 199.
- D. Klomp, T. Maschmeyer, U. Hanefeld and J. A. Peters, *Chem. Eur. J.*, 2004, 10, 2088.
- 31. L. Veum and U. Hanefeld, Chem. Comm., 2006, 825.
- 32. J. M. Guisan, P. Sabuquillo, R. Fernandez-Lafuente, G. Fernandez-Lorente, C. Mateo, P. J. Halling, D. Kennedy, E. Miyata and D. Re, *J. Mol. Catal. B.: Enzymatic*, 2001, 11, 817.