

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Nanosized Pt-containing Al₂O₃ as efficient catalysts to avoid coking and sintering in steam reforming of glycerol

Davi C. Carvalho^a, Helvio S. A. Souza^a, Josué M. Filho^b, Elisbete M. Assaf^c, Vivian V. Thyssen^c, Adriana Campos^d, E. Padron Hernandez^e, Ramon Raudel^e, Alcineia C. Oliveira^{a*}

^aUniversidade Federal do Ceará, Campus do Pici-Bloco 940, Fortaleza, Ceará, Brazil. Phone/fax: 55 85 3366 90 51/ 9982 *Corresponding author: alcineia@ufc.br

^bUniversidade Federal do Ceará, Departamento de Física, bloco 920, Fortaleza, Ceará. Phone/fax: 55 85 3366 94 83.

^cInstituto de Química de São Carlos, Universidade de São Paulo, Av. Trabalhador São-carlense, 400, 13560-970 São Carlos, SP, Brazil

^dCETENE, Av. Prof. Luiz Freire, Cidade Universitária, Recife, Pernambuco, Brazil. Phone/fax: 55 81 33347224.

^eUniversidade Federal de Pernambuco, Departamento de Física – CCEN, Av. Professor Luiz Freire, S/N, Cidade Universitária, 50670-901, Recife-PE, Brazil. Phone:+55-81-91778360.

Abstract

Action of nanosized Pt-containing Al₂O₃ catalysts to avoid coking and sintering was studied in steam reforming of glycerol. The solids exhibited almost 100% conversion toward syngas production at a suitably water to glycerol ratio. Depending on the promoter, a drastic drop in hydrogen yield was observed due to coking and sintering effects. Spent catalysts characterizations by Raman, HRTEM, XRD, TG and SEM-EDS as well as textural properties techniques showed that coking, rather than sintering was the main cause that determine the low hydrogen selectivity of nanosized Pt-containing Al₂O₃ with La₂O₃ or ZrO₂. In contrast, coking did not cover the active sites of Pt-containing Al₂O₃ with MgO or CeO₂. Thus, steam suppressed carbon deposition and improved the nanosized Pt/MgO-Al₂O₃ catalyst stability in steam reforming of glycerol.

Keywords: reforming; glycerol; Raman; deactivation; catalysts.

1. Introduction

Glycerol is produced as a byproduct of biodiesel production. Due to environmental concerns, it is highly desired to develop alternatives for valorization of crude glycerol. Steam reforming of glycerol to hydrogen or syngas production is one of the most attractive options to make use of glycerol, as it can stoichiometrically produce up to 7 mol of hydrogen from 1 mol of the trialcohol (Eq.1).



Although processes mainly based on pyrolysis, autothermal reforming, supercritical water reforming, photo-reforming and aqueous phase reforming of glycerol are potentially suitable for hydrogen production over conventional steam reforming reaction, the amount of hydrogen produced and its selectivity are less based on a thermodynamic analysis¹⁻⁴.

So far, to take full advantage of the benefits of hydrogen as a clean energy carrier, economically viable and environmentally friendly low carbon emitting, catalysts for producing hydrogen are needed. In order to fulfil this, detailed studies of glycerol steam reforming using different catalysts in a fixed-bed reactor have been conducted²⁻⁷. It should be highlighted that due to the high water to organic ratio and the high specific heat of water, the production of hydrogen is favoured. Moreover, upon using steam-to-glycerol ratio in the range of 9–12 and reaction temperature at around 600–700 °C, the steam reforming of glycerol is likely^{1,5}. Thus, nickel-cobalt-based catalysts and noble metal ones are succeeded in steam reforming of glycerol to catalyze most carbohydrates reforming reactions and reforming of methanol, ethanol as well as glycerol, due to chemical similarity of the feedstock^{8, 9-16}. In general, one of the reasons of choice between Pt- and Ni-based catalysts is the resistance to phase transformation and tolerance against sulfur compounds, rather than their

catalytic activity. However, at least in the case of steam reforming of glycerol, platinum-based catalysts appear to be more efficient than Ni ones, which suffer coking more than Pt-based ones and have shorter life^{1,13}.

In this sense, glycerol has ability to decompose over the Pt surface through O–H, C–C and C–H bond dissociations to produce syngas¹. Indeed, Pt surface also has low activity toward C–O bond dissociations, as observed throughout the Fischer–Tropsch and methanation reactions to produce hydrogen. Pt presence also avoids the water gas shift reaction because of the lack of catalytic sites required to activate water^{1,13}.

Concerning the carries, Pt supported on Al₂O₃ catalysts have been widely investigated in steam reforming reactions due to its ability to preventing Pt from incorporation to γ -Al₂O₃ phase, stabilizing Pt⁰ particles and reducing support acidity¹³. Nevertheless, even with a better performance, there is always a need for improving the Pt-based catalysts and also provide the reasons for the deactivation of the solids. As steam reforming of glycerol is endothermic and needs heat to work, this is a harsh reaction condition to operate and would damage the catalysts¹. It is also recognized that the catalytic activity may be enhanced by modifying Al₂O₃ with a small amount of La₂O₃, CeO₂, MgO or ZrO₂¹². This can improve the catalytic activity and stability of the solids for SR reaction. However, coking blocks active sites and increases the amounts of light byproducts such as methane and ethylene, among others. In addition, supports possessing acid properties exhibit low activity to gaseous products and form lateral products owing to dehydration and condensation reactions. Whereas solids prepared through supports with neutral properties allow to obtain catalysts with excellent activity levels to gaseous products in steam reforming of glycerol, high selectivity to hydrogen and stability during long terms stability runs as well¹.

Recently, we have reported a low temperature process for the dry reforming of methane (DRM) to synthesis gas over nanostructured Pt-based catalysts¹⁷. In fact, the deactivation of the catalysts in reason of carbonaceous residues deposition is inevitable in DRM reaction. However, the resistance exhibited by the nanostructured solids against sintering and phase transformation affords expectances to maximize hydrogen production with negligible coke deposition in steam reforming of glycerol reaction.

Thus, the aim of this study is to examine hydrogen production from steam reforming of glycerol using nanostructured catalysts. The study comprises the role played by the structure of the nanostructured oxides to avoid catalysts deactivation. Up to now, it is possible for the reforming process to operate in relatively low temperatures in order to reduce deactivation upon using such solids.

The spent catalysts were characterized by the chemical analysis, nitrogen adsorption desorption measurements, XRD, Raman spectroscopy, HRTEM, TG, and SEM-EDS. The GC-MS are applied to analyze the products from steam reforming of glycerol.

2. Experimental

2.1 Catalyst preparation

Catalyst based on $\text{MeO}_x\text{-Al}_2\text{O}_3$, in which $\text{Me} = \text{MgO}, \text{CeO}_2, \text{La}_2\text{O}_3$ or ZrO_2 were synthesized according to the previous works^{14,15,17}. The detailed procedure was described previously¹⁷. The $\text{MeO}_x/\text{Al}_2\text{O}_3$ ratios were about 20:80 wt%.

Briefly, mesoporous $\text{MeO}_x\text{-Al}_2\text{O}_3$ supports were impregnated with hexachloroplatinic acid (H_2PtCl_6) solution using 1g of each support and the mixture was stirred at 40°C for 2h. The solid was subsequently dried and calcined for 3 h at 350°C in flowing air ($1^\circ\text{C}\cdot\text{min}^{-1}$). The

mesoporous PtO_x/MgO-Al₂O₃, PtO_x/CeO₂-Al₂O₃, PtO_x/CeO₂-La₂O₃ and PtO_x/ZrO₂-Al₂O₃ catalysts were obtained. The nominal amount of Pt was about 1wt%.

The physicochemical properties of the aforesaid fresh catalysts were deeply investigated in our previous work ¹⁷.

2.2. Characterizations of the spent solids

X-ray powder diffraction was used to identify the phases formed after the catalytic test. A X'Pert ProMPD X-ray diffraction equipment having an X-ray generator with CuK α radiation by using 40kV and 40 mA was used for the measurements. The solids were scanned in the range $2\theta = 3-80^\circ$. XRD patterns were compared with those of JCPDS database.

BET surface area, pore volume, and average pore diameter for spent solids were derived from nitrogen adsorption isotherms measured at -196°C in a Micromeritics ASAP 2000. Before the measurement, each sample was degassed at 120°C under vacuum for 10h to remove the adsorbed moisture on the catalyst surface. The pore size distributions were calculated from the desorption branch of isotherms using Barrett–Joyner–Halenda method (BJH).

Laser Raman spectroscopy measurements analyses were performed at room temperature in a LabRam spectrometer (Jobin-Yvon). The emission line at 532 nm from an argon ion laser was focused onto the samples using the macroscopic configuration and samples were examined at low laser power (2 mW) to avoid damage due to laser heating. The device was coupled to an Olympus confocal microscope and a 100 times objective lens was used for simultaneous illumination and collection. Additionally, the device was equipped with a CCD

with the detector cooled to about $-10\text{ }^{\circ}\text{C}$. Ten accumulated spectra were obtained in each spectral range and the spectral resolution was 3 cm^{-1} in the $5\text{-}2000\text{ cm}^{-1}$ range.

High resolution transmission electron (HRTEM) and transmission electron (TEM) micrographs of spent solids were obtained in a FEI Tecnai20 G2 200 kV electron microscope to observe morphology of carbon deposits and particle size. Selected catalysts were ultrasonically dispersed in ethanol and a drop of the suspension was then applied onto clean copper grids and dried at room temperature.

Scanning electron microscopy (SEM) equipped with an energy dispersive analysis system (EDS) measurements were used to study the surface morphology and the element mapping of surface composition of the catalysts. The measurements were conducted on a TESCAN VEGA XMU electron microscope equipped with an EDS Bruker QUANTAX system coupled to the SEM microscope, using an acceleration voltage of 20 kV. Previously, the solids were deposited on an aluminium sample holder and sputtered with gold and then SEM measurements were conducted.

Amounts of carbon deposits were obtained by thermogravimetric analysis (TG) coupled to differential scanning calorimetry (DSC) apparatus in a Netzsch STA 409 PC/PG equipment coupled to a Bruker Tensor 27 IR instrument, under air stream between 50 and 1000°C at a rate of $10^{\circ}\text{C}\cdot\text{min}^{-1}$.

2.3. Activity testing

Catalytic tests in steam reforming of glycerol were performed in a quartz fixed-bed reactor with 39 cm and 1 cm of inner diameter. Blank runs were performed prior to the catalytic reactions and conversion of glycerol values was negligible. Typically, 100 mg catalysts were sandwiched by quartz wool and packed in the reactor and activated *in situ* under a gas mixture

of hydrogen and nitrogen at 600°C for 1 h with hydrogen flow of 30 cm³.min⁻¹. Thereafter, the system was purged flowing nitrogen while it reached the reaction temperature. A thermocouple was inserted into the centre of the catalytic bed to monitor the reaction temperature. A mixture of water to glycerol ratio of 9:1 was fed into the reactor through a high-precision pump. The cold trap contained the liquid products which were analysed without preliminary extraction or separation using a gas chromatograph (Shimadzu,) equipped with a FID detector and HP5 capillary column and operating between 35 and 250°C with hydrogen as carrier gas.

Gaseous samples were analyzed using gas chromatograph Varian Chrompack GC-3800 using hydrogen as carrier gas. The chromatograph was equipped with two packed columns, namely Porapak-N and Molecular Sieve 13X and operates between 40 and 80°C with a carrier gas of He and N₂, respectively, flowing at 10 mL min⁻¹. The carbon balances were about 5% in errors.

3. Results and discussion

3.1. Catalytic performances of the solids in steam reforming of glycerol

Characterizations of the fresh catalysts have been described in detail in our previous paper that contains a summary of the main features of the catalysts screened ¹⁷.

Conversion values in steam reforming of glycerol are shown in Table 1.

Table 1

The catalysts exhibit high efficiency in steam reforming of glycerol with optimized reaction conditions along of 300h time on stream. According to the Table, glycerol conversion is maximum for the PtO_x/MgO-Al₂O₃. It is evident that the other catalysts show significant

performances with respect to that PtO_x/MgO-Al₂O₃, except for PtO_x/CeO₂-La₂O₃ whose performance is the lowest among the solids studied. The H₂/CO₂ ratios are indicative of the yields of gaseous products. The findings states that the theoretical ratios for glycerol steam reforming is close to 2.3 (mol/mol)^{1,7}. Thus, the H₂/CO₂ ratio obtained are similar and agree with those predicted theoretically value and it may suggest an optimal behaviour for steam reforming of glycerol. On the other hand, values of H₂/CO ratio between 5.0 and 7.0 indicate the presence of side reactions such as glycerol decomposition to hydrogen and carbon and reverse water gas shift (RWGS) reaction, among others, as shown elsewhere¹⁸.

Fig.1 shows plots of yields and selectivity of the products obtained versus time on stream.

Fig.1

Both gaseous and liquid products are obtained by chromatogram analyses over all catalysts. The hydrogen yield is about 7.0 within ca. 5 h over PtO_x/ZrO₂-Al₂O₃ due to the complete steam reforming (Fig.1a) leading to similar production of hydrogen, as that observed for PtO_x/MgO-Al₂O₃. Similar results are seen for gas compositions over the aforesaid catalyst at space velocity as low as 0.25 h⁻¹(Fig. 1b). The elevated hydrogen production is believed to be from the well dispersion of Pt on the support, as previously observed¹⁷. However, sintering of particles from PtO_x/ZrO₂-La₂O₃ and PtO_x/MgO-Al₂O₃ at the expense of faster coking rates can further explain these results. Moreover, relatively low amounts of CO₂ and CO are produced over these solids, owing to the reverse water gas shift (RWGS) reaction occurrence whereas CH₄ production is negligible.

Hydrogen yields for CeO₂-containing catalysts achieve values below to 5 comparing with the other catalysts. Such an effect can be expected to be resulted from the different types of interaction of CeO₂ with La₂O₃ and Al₂O₃. The role of CeO₂-in tuning structural properties

could be a result of presence of a stable phase e.g., CeAlO₃ combined with its high surface area, which promote the dispersion of the Pt⁰ nanoparticles, as observed for dry reforming of methane¹⁷. This not the case of the interaction between CeO₂ with La₂O₃, whose a huge mismatch between fast carbon deposition (latter shown in spent catalysts characterizations) and reduction/oxidation cycles of CeO₂ as well as a mobile surface oxygen species transferred to Pt are observed¹⁹. The yields of CO and CO₂ are rather limited to the impurity amounts.

Although the conversions of glycerol over PtO_x/ZrO₂-Al₂O₃ and PtO_x/MgO-Al₂O₃ are slightly higher than those Ce-containing catalysts, the formers have very close H₂ selectivity (about 55%, Fig.1a). The hydrogen selectivity decreases with time on stream in reason of hydrogen in water favouring the hydrogen production via Water Gas Shift (WGS) reaction over PtO_x/ZrO₂-Al₂O₃ at the beginning of the reaction and a further stabilization of hydrogen production is observed. The same linearity is shown for PtO_x/MgO-Al₂O₃ and hydrogen selectivity is always 55%, suggesting that the mechanisms of hydrogen production are the same for these two catalysts. Meanwhile, the selectivities of CO₂ and CO experience an increase at the beginning of the reaction and subsequently drop, being quite low at the end of the catalytic runs. This observation also suggests that possible phase transformations may be occurred over PtO_x/ZrO₂-Al₂O₃ while MgO modification on PtO_x/Al₂O₃, led to similar changes in H₂ due to sintering (further shown by TEM and XRD). Moreover, very low detectable amounts of CO, CH₄ and CO₂ (below 20%) and undesired C₂H₄ can be observed in the short-term stability run over both PtO_x/ZrO₂-Al₂O₃ and PtO_x/MgO-Al₂O₃, demonstrating that the hydrogen production is facilitated over these solids.

Both PtO_x/CeO₂-Al₂O₃ and PtO_x/CeO₂-La₂O₃ demonstrate that the H₂ selectivity has a plateau by ca. 54% within ca. 5 h on stream whereas CO₂ and CO selectivities are 20%.

Despite the low hydrogen yield, PtO_x/CeO₂-La₂O₃ has elevated selectivity to the gaseous products. This important aspect implies the CeO₂ combined with La₂O₃ facilitate the formation of CO₂ and water by WGS reaction providing a pathway for removing adsorbed CO from the Pt surface and thus inhibiting reforming reactions by blocking surface sites²⁰. In addition, the elevated C₂H₄ selectivity indicates that coking caused by polymerization is not beneficial for hydrogen production.

In case of condensate liquid effluents, analyses show that the small amounts of byproducts are formed. There are formic and propionic acids, acetone, diols, acetone, ethanol, glycidol, sorbitol, propylene glycol and dioxolanes, which are detected in the condensate.

Traces of higher molecular weight condensation products are also found over PtO_x/CeO₂-Al₂O₃ and PtO_x/CeO₂-La₂O₃, confirming the existence of coke precursor over these solids.

Studies lead on PtO_x/CeO₂-Al₂O₃ and PtO_x/MgO-La₂O₃ reveal that the yield of the products and selectivity decay for much longer space velocity (up to 0.25 h⁻¹, Fig.1c). Comparisons between Fig. 1b and 1c show the effect of space velocity process variable over product distribution and glycerol conversion. As it can be seen, lower glycerol conversion and hydrogen yield as well as change of CO product distribution (H₂/CO₂ ratio of 6.0) are observed with increase in space velocity. Besides, the yields of methane and CO₂ are also negligible under these conditions. These behaviors suggest that CO seems to be formed by consecutive reactions such as RWGS reaction. Thermodynamic analyses for steam reforming of glycerol based on non-stoichiometric approach shows that the hydrogen yield value at equilibrium is found to be 6.86 with dilute feed system containing 10 wt% of glycerol⁹. Thus, the hydrogen yield is far from equilibrium using space velocity higher than 0.25 h⁻¹ and lower glycerol feed concentration (i.e. 10 wt% glycerol).

Extended tests over longer periods up to 12 h results are shown in Fig. 1d. The hydrogen production on PtO_x/MgO-Al₂O₃ is particularly high, showing approximately 6 mol.mol⁻¹ of glycerol supplied greater yield than on PtO_x/CeO₂-Al₂O₃ and the H₂/CO ratio is ca. 7.5 as well. Following the same trends, conversion of glycerol remains nearly 100% and 97% for PtO_x/MgO-Al₂O₃ and PtO_x/CeO₂-Al₂O₃, respectively. In addition, the production of methane, carbon monoxide and carbon dioxide is negligible over both catalysts studied. Besides, the yield of H₂ and glycerol conversion becomes small over PtO_x/CeO₂-Al₂O₃ by using a space velocity of 0.5h⁻¹ while no change of the products distribution is observed.

Nevertheless, the activity of the catalysts differs depending upon whether more carbon deposition would form with increasing the time on stream. Thereby, it seems that unless coking can be removed on catalyst surface, a lesser hydrogen production would be observed on the solids. These results indicate superior catalytic properties in PtO_x/MgO-Al₂O₃ and appear to be attributed primarily to the ability of avoiding hard coking deposition. This data are further confirmed by spent catalysts characterization results. Moreover, the conversion of the solids is higher than that of unprompted 1 wt% Pt/Al₂O₃ catalyt.¹

3.2. Characterizations of spent catalysts

3.2.1 XRD and Raman measurements

XRD patterns of the spent catalysts are shown in Fig. 2. All catalysts displays the main peaks at approximately 2θ equal to 33, 37, 49 and 68°, which corresponded, respectively to the (111), (220), (311), (400) and (440) planes of the R₃C type structure of γ-Al₂O₃ (JCPDS 46-1131). For PtO_x/ZrO₂-Al₂O₃, the diffraction pattern contains any peaks of ZrO₂ with tetragonal symmetry, belonging to P42/nmc space group at around 2θ = 30, 35, 50, 60 and 74°

regions of the XRD pattern. These peaks are indexed to be from (101), (002), (112), (211) and (200) reflexions and can be overlapped with those of alumina. Furthermore, the intensities of the peaks indicate that metal particles are too big to produce the aforesaid reflections. This observation is in agreement with the metal particle size of 35 nm for (002) plane of t-ZrO₂ as calculated from Scherer equation and also suggest sintering of the solid. No other characteristic peaks of platinum oxide phases eventually formed are detected owing to the superimposition with the aforesaid phases.

Fig.2

In case of PtO_x/MgO-Al₂O₃, the broad diffraction peaks ascribable to cubic MgO (JCPDS 4-829) are present with reflexions at 2θ = 42 and 62°, respectively corresponding to (220) and (200) planes together with those of γ-Al₂O₃. Moreover, weak diffraction peaks of PtO_x species may be suggested, but they are at the same position of the MgAl₂O₄ at about 2θ = 20, 31, 37, 45, 56, 60 and 65°, corresponding to the reflexions of a Fd-3m cubic spinel oxide (JCPDS-21-1152). Another possibility is that Pt particles are highly dispersed with the crystallite size beyond the detection limit of XRD. The findings states that during reforming of hydrocarbons reactions lead with Pt supported on MgAl₂O₄ catalysts, phase transformations of MgAl₂O₄ to MgO and γ-Al₂O₃, decrease the catalytic performance of the solid¹⁴. In addition, no diffraction peaks of metallic platinum are discernable over PtO_x/ZrO₂-Al₂O₃ and PtO_x/MgO-Al₂O₃, indicating that Pt could be highly dispersed. Graphite peak is also detected in small intense peaks around 2θ equal to 26° (002) and 44° (101). These assumptions suggest that sintering and phase transformations are the leading causes of the decrease of the catalytic performance of PtO_x/ZrO₂-Al₂O₃ at the beginning of the reaction; but this factor may not

cause the deactivation of the solid. For PtO_x/MgO-Al₂O₃, all of these factors together with coking contribute do not decrease the hydrogen production.

Spent PtO_x/CeO₂-Al₂O₃ yields a broad diffraction pattern containing peaks at $2\theta = 34$ (111) and 55° (220) belonging to the Fd-3m of cubic CeO₂. This pattern closely match the pattern for cubic fluorite type structure of CeO₂^{15,19}, besides the aforesaid peaks of γ -Al₂O₃. Also, this pattern suggests the presence of an interaction between CeO₂ and Al₂O₃ to produce R₃-C cubic CeAlO₃ structure with the typical peak at 37° (110)¹⁵, with the absence of unalloyed Pt and support. The presence of graphite phase at $2\theta = 25$ and 43° is consistent with the (002) (101) planes, which predicts the coexistence of carbonaceous deposits over the spent solid. Based on the Scherrer equation and the most intensive CeO₂ (111) diffraction peak, the average crystallite size of magnetite was estimated to be ca. 10 nm. Platinum peaks are not visible in the diffraction patterns probably due to the superimposition of the peaks. These facts accounts for a minor performance concerning to hydrogen yield of PtO_x/CeO₂-Al₂O₃, as compared to those of PtO_x/ZrO₂-Al₂O₃ and PtO_x/MgO-Al₂O₃.

The addition of La₂O₃ instead of Al₂O₃ on PtO_x/CeO₂-La₂O₃ seems to not change the XRD pattern comparing with spent PtO_x/CeO₂-Al₂O₃. This feature is attributed to the incorporation of the CeO₂ on lanthana framework forming a solid solution. The presence of the diffraction peaks at $2\theta=35$ and 55° may be assigned to the (111) and (220) planes of CeO₂. Lanthana presence could be suggested at $2\theta=26$ and 30° , which is assigned to hexagonal La₂O₃ (JCPDS 74-2430) but these reflexions appear in the same region of ceria; thereby, it is not possible to ascertain the presence of this oxide. Platinum phases are not seen, indicating a well-dispersed Pt structure on the surface of the support.

Crystallite size is calculated from X-ray line broadening of CeO₂ (111) using the Scherrer equation and the value is not obtained for PtO_x/CeO₂-La₂O₃ due to the broadness of the diffractogram. The slight intensity of the graphite observed for PtO_x/CeO₂-La₂O₃ at about at 2θ=26 and 42° suggests that hard coking happened instead of crystal growth.

In addition, according to the JCPDS card number 01-1190, metallic platinum is commonly observed at around 2θ=39.8 (111), 46.5 (200) and 67.8° (220). However, these peaks are not visible for all spent solids due to either overlap Pt peaks with those of the other phases or even the possible dispersion of Pt particles to undetectable sizes.

Glycerol has lower potential to form solid carbon in steam reforming reaction¹. However, studies on Raman spectroscopy suggest that carbonaceous deposition is induced by some type of catalysts. To confirm this hypothesis, Raman spectra of the spent solids are shown in Fig.3.

Fig.3

The shape and the broadness of the spectra of PtO_x/CeO₂-La₂O₃, PtO_x/CeO₂-Al₂O₃ and PtO_x/MgO-Al₂O₃, especially for vibrational modes at high wavenumbers confirm that carbonaceous deposits are formed during the catalytic runs. This interpretation is consistent with the fact that other studies have shown coking in steam reforming of hydrocarbons reaction over Pt or Ni-based catalysts²¹⁻²³.

The appearance of a strong mode at around 460 cm⁻¹ in PtO_x/CeO₂-Al₂O₃ means the F_{2g} mode of fluorite CeO₂ is clearly visible. In addition, the defects modes at around 610 cm⁻¹ of Ce-based oxides^{14,15} could not be detected due to its low intensity. This indicates that the phases such as CeO₂ and CeAlO₃ are present in the solid, in agreement with XRD results. At high frequencies, the Raman fingerprint of disordered Csp²-based materials are found at around 1350 (D band) and 1585 cm⁻¹ (G band) assigned to phonons of E_{2g} and A_{1g} symmetry,

respectively. The D band is attributed to be caused by defects and disorder in the graphene-like structure whereas the G band is associated with the first-order scattering of the E_{2g} mode of in-plane sp^2 carbon single bond stretching vibrations from graphite sheets^{11,22,24,25}. These modes definitely prove that disordered carbonaceous deposits always form on catalyst surface from C-C bond breakage of glycerol and their byproducts. Moreover, $PtO_x/CeO_2-La_2O_3$ spectrum shows the D' band at about $1605-1620\text{ cm}^{-1}$, which is due to the stretching of C=C bonds carbon of less structured coke or graphite-like structures^{24,25}. In addition, two distinct broad modes with maxima at around 2652 and 2930 cm^{-1} are attributed to presence of defects, including the edges of the nanotubes in the so called G' (or 2D) band²⁶.

A comparison between $PtO_x/CeO_2-Al_2O_3$ and $PtO_x/CeO_2-La_2O_3$ spectra show distinct features concerning the intensity, position, and width of the modes. This suggest that deformation taking place in the crystal structure due to the larger ionic radius of La^{3+} compared to Ce^{4+} as well as the lattice expansion and the presence of oxygen vacancies over $PtO_x/CeO_2-La_2O_3$, as for Ce-La based catalysts applied to SR of ethanol²⁷. Literature reports that modes at around $350-400\text{ cm}^{-1}$ region are assumed to be from fundamental modes of La-O²⁸. However, overlapping of the modes with those of CeO_2 does not allow lanthanum oxides identification. Besides, a hard carbon deposit on catalyst surface is considered a main cause of catalyst deactivation of $PtO_x/CeO_2-La_2O_3$, as already predicted by XRD.

Of similar features is the $PtO_x/MgO-Al_2O_3$ spectrum, which the G and D modes dominate the Raman spectrum together with an additional broad mode emerges at around 3227 cm^{-1} due to water presence.

The structural characterization of the deposited coke is taken from the intensity ratio of the I_D/I_G bands. According the findings, defects formation increases the I_D/I_G ratio but increases

the I_{2D}/I_G ratio²⁶. Noticeably, the ratio between the areas of the D and G bands of ca. 0.32 from PtO_x/MgO-Al₂O₃ indicates that the degree of graphitization of carbonaceous deposits greater than the other samples. Conversely, the D-to-G intensity ratio increases for 0.49 over PtO_x/CeO₂-Al₂O₃ in line with deposition of both low-graphitic coke with only few structural defects and amorphous carbonaceous deposits formation. Instead, deposition of amorphous carbon is observed for PtO_x/CeO₂-La₂O₃ with the I_D/I_G ratio of 0.57. Regarding the these results, the harsh coking from graphite type-carbon deposits accounts for the decrease performance of PtO_x/MgO-Al₂O₃ and PtO_x/CeO₂-La₂O₃ catalysts whereas correspondingly amorphous coke formation may be smoothly removed by steam and this not diminish PtO_x/MgO-Al₂O₃ performance. It may be possible that this kind of coke may be from the formation of olefinic chains and aromatic rings, as for magnesia and alumina-based catalysts tested in glycerol steam reforming²¹.

Raman spectrum of PtO_x/ZrO₂-Al₂O₃ displays modes at around 319 (E_g), and 634 cm⁻¹ (B_{1g}) due to tetragonal (P42/nmc (D_{4h}¹⁵) space group) and monoclinic (P21/c (C_{2h}⁵) space group) phases of ZrO₂²⁹. This means that the typical of both tetragonal and monoclinic ZrO₂ phases are present in the in segregated phases confirming the hypothesis of sintering of the solid after the catalytic test. A strong luminescence caused by alumina impedes the other modes identification. It is most likely that PtO_x/ZrO₂-Al₂O₃ is deactivated by phase transformation and sintering instead of carbon deposition, since carbon modes are not visible by Raman spectroscopy.

3.2.2 TEM and Surface texture of the solids

TEM images of the spent catalysts are shown in Fig. 4.

Fig.4

It can be seen that the spent $\text{PtO}_x/\text{CeO}_2\text{-Al}_2\text{O}_3$ (Fig.4a₁) exhibits the characteristic rod-like carbon morphology, similar to that of carbon nanotubes. The value of d spacing of ca 0.225 nm, from (111) plane as well as dispersed black spots, confirm the Pt nanoparticles remains intact after the catalytic test and possess varying between 5 to 12 nm. In addition, these nanoparticles are in a well dispersed fashion and the nanoparticles sizes values close to that obtained XRD results. It is further illustrated the presence of typical carbonaceous deposits formation in Fig.4b₁. Filamentous and carbon nanotubes formation are likely on the spent solid. Moreover, nanoscale Pt metal particles possessing diameters ranging from 0.5 to 2 nm are very evident inside the tubes along with amorphous carbon (Fig.4a₁). It might be possible that on $\text{PtO}_x/\text{CeO}_2\text{-Al}_2\text{O}_3$ surface, the decomposition of glycerol and the subsequent layers of carbonaceous species deposition start to form on Pt sites of active metals for shorter duration; however, a slight hindrance of the activity of the solid is observed due to carbon gasification towards CO_2 formed during the reaction, as observed in the catalytic results.

TEM micrograph of $\text{PtO}_x/\text{CeO}_2\text{-La}_2\text{O}_3$ (Fig 4a₂) illustrates domains possessing a high degree of crystallinity resulting in a needle-like structure and a corrugated surface with repeating ridges. HRTEM image (Fig 4b₂) displays transparent carbon sheets with crumpled silk veil waves and the rumples are involved by the Pt nanoparticles, which has an average size of approximately 6–18 nm. In addition, fringes of several crystallites in different orientations can be seen from an electron diffraction pattern including the layered carbon nanostructures. Also, the crystal lattice fringes reveal that these particles are from highly crystalline features of Pt. These features suggest that deactivation of $\text{PtO}_x/\text{CeO}_2\text{-La}_2\text{O}_3$ is mainly due to coking in agreement with previous Raman and XRD results. The Ce-La solid solution formation is formed during the catalytic test consisting with the results based on

literature²⁷. This might be induced further a crystal growth and thereby, formation of the aforesaid crystal type-structure results in a low performance of the solid in the SR reaction. Additionally, the findings states that carbon species formed on metallic sites may be partially removed by oxygen species originating from lanthanum carbonate species such as $\text{La}_2\text{O}_2\text{CO}_3$ ⁷. However, this phenomenon is not observed for $\text{PtO}_x/\text{CeO}_2\text{-La}_2\text{O}_3$, judging from its low performance in the reaction.

It is clearly seen that the TEM image of $\text{PtO}_x/\text{ZrO}_2\text{-Al}_2\text{O}_3$ (Fig 3a₃) exhibits large particles occupying almost of the entire of solid surface. These particles are indeed densely aggregated with fairly even distribution (Fig 3b₃), which indicate the strong interaction between the Pt nanoparticles and the $\text{ZrO}_2\text{-Al}_2\text{O}_3$. The characteristics of a crystalline Pt face centred cubic structure is confirmed by d-spacings of the lattice fringes at around 0.225 nm, which can be indexed to as the (111) crystalline plane of Pt³⁰. The lattice distances of the Al_2O_3 obtained from high-resolution TEM (HRTEM) image (e.g., 0.7 nm) and t- ZrO_2 (belonging to the P42/nmc space group possessing $d=0.284$ nm from (111) planes with JCPDS number card 37-1484) are clearly visible. The particles particle sizes obtained are estimated to be 39 nm, in average and this is in coherence with the data obtained from XRD patterns. From these results, it can be confirmed that the cause of deactivation of $\text{PtO}_x/\text{ZrO}_2\text{-Al}_2\text{O}_3$ catalyst is sintering of Pt particles and phase transformations.

Based on TEM measurements of $\text{PtO}_x/\text{MgO-Al}_2\text{O}_3$ (Fig.4 a₄), agglomeration of Pt particles in random regions with an average particle size of 10-30 nm is observed. The edges of the particles area are all surrounded by carbonaceous species, which are supposed to be from carbon whiskers fibers formed during the glycerol steam reforming tests (Fig.4b₄). Although some metal particles encapsulated within the filaments could help the side WGS reaction and

carbon formation with an auto consumption process during reforming process³¹, coke formation together with sintering contributes to decrease the catalytic properties of the solid, which is consistent with the XRD and Raman results.

Table 1 displays the textural properties of spent catalysts. The fresh catalysts are mesoporous materials that possess elevated textural properties¹⁷. It seems that some of the catalyst pores might have suffered by sintering and carbonaceous deposits formation on solid surface and thus, affecting the textural properties.

Contrary to the abovementioned expectation, the unchanged surface area of ca. 83 m².g⁻¹ and pore volume of ca.0.12 cm³.g⁻¹ registered for PtO_x/CeO₂-Al₂O₃ may be attributed to a lesser intensity of the catalytic deactivation, probably. This implied that carbon entities formed on spent catalyst neither occupy the active sites nor cover the Pt site, consequently these fact did not impair the activity of the solid. BET surface, pore volume and pore size of the other samples decrease after catalytic evaluation. It is noted that surface area is reduced from 143 m² g⁻¹ for the fresh PtO_x/ZrO₂-Al₂O₃ to 73 m² g⁻¹, which is considered to be a drastic reduction due to sintering effects, as observed previously by the other characterization techniques. In case of PtO_x/MgO-Al₂O₃, the textural properties remain almost unaltered, thereby, it can be regarded that coking is eliminated on the solid surface as soon as it is formed and this accounts for the best catalytic properties of the solid. For PtO_x/CeO₂-La₂O₃, a drop of the BET surface area and pore volume is observed compared to the fresh solid, suggesting the coke is not vanished from solid surface resulting in a low catalytic performance of the solid. The pore diameter of the spent catalyst is adequate (2.8-4.5 nm) to allow the reforming reaction occurring inside the inner channels because it was much greater than the size of glycerol molecule which is around 0.62 nm³. Even if the pores of PtO_x/CeO₂-

Al_2O_3 and $\text{PtO}_x/\text{ZrO}_2\text{-Al}_2\text{O}_3$ experience a decreased due to sintering, it is likely that deactivation may be not due to the diffusion limitation of the reactants or products.

3.2.3 SEM-EDS and TG analyses

Fig. 5 exhibits the SEM-EDS micrographs of the spent solids. It seems that the morphology of spent $\text{PtO}_x/\text{CeO}_2\text{-La}_2\text{O}_3$ (Fig. 5a₁) consists of coke deposits in which nanofibers are noticed. Elemental maps of the main elements such as Pt, Al, Ce, La and C from the sample area suggest a heterogeneous distribution of carbon on solid surface. According to the above Raman, TEM and XRD predictions, the carbonaceous deposits (both amorphous and graphitic) on solid surface is the main cause of the lesser performance of $\text{PtO}_x/\text{CeO}_2\text{-La}_2\text{O}_3$ to hydrogen production from steam reforming of glycerol. SEM micrograph of $\text{PtO}_x/\text{CeO}_2\text{-Al}_2\text{O}_3$ suggests the formation of aggregates of nanoparticles, probably from the segregated CeO_x island. Nevertheless, this could be a moderate accumulation of CeO_x particles, as proved previously by TEM image of the solid. The corresponding EDS spectrum (Fig. 5a₂), a quite uniform distribution of Pt and Al is observed, besides the expected carbon presence, which tends to be accumulated on spent $\text{PtO}_x/\text{CeO}_2\text{-Al}_2\text{O}_3$ surface.

As seen from SEM image of $\text{PtO}_x/\text{MgO-Al}_2\text{O}_3$, the solid surface is composed of very bulky spherical-like particles. These particles are coated by a carbon layer in which carbon fibers and carbon nanotubes are observed, as indicated previously by Raman spectroscopy. As EDS spectrum suggests an homogeneous distribution of Al, Mg and Pt elements, it would be indicated that carbon deposition does not cover the active sites and the morphological and textural properties of the solid remains unaltered. This is also observed for Ni-based catalysts

in the glycerol steam reforming^{31,32} and coking do not damage the catalytic performance of the solid.

SEM image of PtO_x/ZrO₂-Al₂O₃ shows the sintering of the particles of after reaction, since aggregation of particles is noted. The EDS spectrum of the solid displays the signals of the main elements such as Zr, Al, Pt and C, in which the content of the latter is too low and any kind of heterogeneity of the composition is definitely shown.

TG analysis of PtO_x/CeO₂-La₂O₃ after catalytic run reveals the occurrence of a mass loss in the first step (25–150°C), which is assigned to removal of adsorbed water. A subsequent significant mass loss is observed in the 150-350 °C is due to the elimination of interstitial water and combustion of amorphous carbonaceous species originated from glycerol decomposition to other organic by-products that can be adsorbed on the surface covering the active sites, and in some extent blocking the catalyst pores⁴. The IR curves from TG experiments are included in Supplementary information. According to the findings, amorphous carbon oxidizes below 550 °C whereas graphitic/filamentous carbon does at higher temperature³³. The third weight loss event, with a highest mass loss is observed at around 400-800 °C, being ascribed to the graphitic carbon elimination at elevated temperatures. As reported in the literature³³, under steam reforming conditions, coking gasification is promoted by water in steam reforming reactions. This could indeed result in structural defects, such as vacancies, face edges and among others defects on the solid. With this in mind, the weight loss of ca. 1% on PtO_x/CeO₂-La₂O₃ might be result of previous coking removal by steam and oxidation of CeO₂ to create such defects could be likely.

A comparison between PtO_x/CeO₂-La₂O₃ and PtO_x/CeO₂-Al₂O₃ curves shows that the weight loss of the latter is divided in two events. The first one is observed at around 25-350°C

temperature range, which is ascribed to the removal of interstitial water and/or the oxidation of the amorphous carbonaceous species, as previously suggested by Raman spectroscopy. The second event peak is very wide and oxidation of carbon deposits take place in the 300-700°C, and overlaps graphitic carbonaceous species oxidation and re-oxidation oxidation of CeO₂ and Pt atoms. The 2% amount of coke deposited on the solid is a result of the formation rate minus the gasification rate, which accounts for the lower coke amount found on PtO_x/CeO₂-Al₂O₃, in agreement with SEM-EDS results.

TG curve of spent PtO_x/MgO-Al₂O₃ shows only one weight loss event that occurred at around 25-400 °C is due to the formed coke elimination at lower temperatures. It has being stated that Mg and Ca incorporation to catalysts can enhance the steam gasification of coke by activating water adsorption³³ and thus, this accounts for the better performance of this solid, even if graphite carbon is majoritary formed during SR (Raman spectroscopy). The TG curve of PtO_x/ZrO₂-Al₂O₃ does not seem to undergo any difference concerning the unique event observed. However, it might be a result of the evaporation of occluded water and the oxidation of the aggregated particle, since a low amount of coke is deposited on the solid surface. These results are consistent with those obtained by SEM-EDS and Raman analyses.

4. Conclusions

Pt-containing MeO_x-Al₂O₃ catalysts were evaluated in glycerol steam reforming. Using MgO and CeO₂ promoters, the solids had elevated glycerol conversions and selectively produced hydrogen with low yields to byproducts whereas La₂O₃ and ZrO₂ promoters were found to be lesser selectives to hydrogen production. Spent catalysts characterizations by Raman, TEM, XRD, TG and SEM-EDS as well as textural properties techniques showed that

coking, rather than sintering is the main cause that determine the low hydrogen selectivity of the solids. The coking did not cover the active sites of Pt/ MgO-Al₂O₃ and Pt/CeO₂-Al₂O₃ and steam suppress carbon deposition, and thus improve the catalyst stability in steam reforming of glycerol.

5. Acknowledgments

The financial supports of this work by CNPq with contract n^o 490162/2011-8 and Funcap (areas estrategicas 2011 project) are gratefully acknowledged. We would like to thank CETENE-INT for TEM measurements as well as Dr. A. J de Paula for SEM-EDX analyses at Central Analitica da UFC.

6. References



1. N. H. Tran, G. S. Kamali Kannangar, *Chem.Soc. Rev.* 2013, **42**,9454.
2. L. P.R. Profeti, E. A. Ticianelli, E. M. Assaf, *Int J Hydrogen Energy* 2009,**34**,5049.
3. S.Li,J. Gong,*Chem. Soc. Rev.*, 2015, in press. Doi: 10.1039/C4CS00223G.
- 4.G. Sadanandam, K. Ramya, D. B. Kishore, V.Durgakumari, M.Subrahmanyam, K.V. R. Chary, *RSC Adv.*, 2014,**4**, 32429.
5. T. A. Maia,E. M. Assaf, *RSC Adv.*, 2014,**4**, 31142.
- 6.G.Wu, S. Li, C. Zhang, T.Wang, J. Gong,*Appl. Catal. B: Environm*, 2014, **144**, 277.
7. V. V. Thyssen, T. A. Maia, E. M. Assaf, *Fuel*,2013,**105**, 358.
- 8.T.Montini, R.Singh, P.Das,B. Lorenzut, N.Bertero, P. Riello, A. Benedetti, G. Giambastiani, C Bianchini, S. Zinoviev, S. Miertus, P Fornasiero, *ChemSusChem* 2010,**3** 619.
9. C. D. Dave, K.K. Pant, *Renewable Energy*,2011,**36**, 3195.


10. A.Iriondo, V.Barrio, J.Cambra, P.Arias, M.Guemez, M.Sanchez, R. Navarro, J.L. Fierro,*Int J Hydrogen Energy*,2010,**35**, 11622.
11. M. M. Rahman, T. L. Church, M. F. Variava, A. T. Harris, A. I. Minett ,*RSC Adv.*, 2014,**4**, 18951.
12. I. Rossetti, J. Lasso, V.Nichele, M. Signoretto, E.Finocchio, G. Ramis, A.Di Michele *Appl.Catal. B: Environm.*2014,**150–151**, 257.
13. E.L. Kunkes, D. A. Simonetti, J. A. Dumesic, W. D. Pyrz, L. E. Murillo, J.G. Chen, D. J. Buttrey, *J. Catal.*,2008,**260**, 164.
14. H. S. A. de Sousa, A. N. da Silva, A.J.R. Castro, A. Campos, J. M. Filho, A. C. Oliveira,*Int J Hydrogen Energy* 2012,**37**, 12281.
- 15.F. F. de Sousa, H. S.A. de Sousa, A.C. Oliveira,M. C.C. Junior, A. P. Ayala, E. B. Barros, B. C. Viana, J. M. Filho, A. C. Oliveira, *Int J Hydrogen Energy* 2012,**37**,3201.
16. K. Seung-hoon, J. Jae-sun, Y. Eun-hyeok, L. Kwan-Young, M. D. Ju, *Catal. Today*,2014,**228**, 145.
17. D.C. Carvalho, H. S.A. De Souza, J. M. Filho, A.C. Oliveira, A. Campos, É. R.C. Milet, F. F. de Sousa, E.P. Hernández, A.C. Oliveira, *Appl. Catal. A: Gen.*, 2014,**473**, 132.
18. C. A. Franchini, W.Aranzaez, A.M. Duarte de Farias, Gina Pecchi, M. A. Fraga, *Appl. Catal.B: Environm.*2014,**147**,193.
19. P.Pantu, G.R. Gavalas, *Appl Catal A: Gen* 2002,**223**, 253.
20. J.W. Shabaker, R.R. Davd, G.W. Huber, R.D. Cortright, J.A. Dumesic, *J.Catal.* 2003, **215**, 344.
21. B. Valle, B. Aramburu, A.Remiro, J. Bilbao, A.G. Gayubo, *Appl.Catal.B: Environm.* 2014,**147**, 402.

22. M. El Doukkali, A. Iriondo, P.L. Arias, J.F. Cambra, I. Gandarias, V.L. Barrio, *Int. J. Hydrogen Energy* 2012, **37**, 8298.
23. L. He, J.M.S. Parra, E. A. Blekkan, De Chen, *Energy Environ. Sci.*, 2010, **3**, 1046.
24. A. Serrano-Lotina, L. Daza, *Appl. Catal. A: Gen.* 2014, **474**, 107.
25. W. Donphai, K. Faungnawakij, M. Chareonpanich, J. Limtrakul, *Appl. Catal. A: Gen.* 2014, **475**, 16.
26. A.O. Al-Youbi, J.L. Gómez de la Fuente, F.J. Pérez-Alonso, A. Y. Obaid, J.L.G. Fierro, M.A. Peña, M. Abdel Salam, S. Rojas, *Appl. Catal. B: Environm.* 2014, **150–151**, 21.
27. X. Han, Y. Yu, H. He, W. Shan, *Int. J. Hydrogen Energy* 2013, **38**, 10293.
28. B.M. Faroldi, J. F. Múnera, L. M. Cornaglia, *Appl. Catal. B: Environm.* 2014, **150–151** 126.
29. R. Pazhani, H. P. Kumar, A. Varghese, A. M. E. Raj, S. Solomon, J.K. Thomas, *J. Alloys Compounds* 2011, **509**, 6819–6823.
30. M. Zhang, J. Xie, Qian Sun, Zaoxue Yan, Min Chen, Junjie Jing, *Int. J. Hydrogen Energy*, 2013, **38**, 16402. [31] J. Segner, C.T. Campbell, G. Doyen, G. Ertl, 1984. Catalytic oxidation of CO on Pt (111): the influence of surface defects and composition on the reaction dynamics. *Surf. Sci.* **138**, 505.
32. L.F. Bobadilla, A. Álvarez, M.I. Domínguez, F. Romero-Sarria, M.A. Centeno, M. Montes, J.A. Odriozola, *Appl. Catal. B: Environm.* 2012, **123–124**, 379.
33. J.A. Calles, A. Carrero, A.J. Vizcaíno, L. García-Moreno, *Catal Today*, 2014, **227**, 198.


Figures



Fig. 1. Short-term catalytic runs over the catalysts studied. (a) Yield of gaseous products formed (b) Selectivity to the products obtained. Reaction conditions: fixed temperature (600°C), time of 5h, water to glycerol ratio of 9 and space velocity of 0.25 h⁻¹ (c) Yield of gaseous products formed and selectivity to the products obtained. Reaction conditions: fixed temperature (600°C), time 5h and water to glycerol ratio of 9 and space velocity of 0.5 h⁻¹ (d) Long term stability runs over the PtO_x/ MgO-Al₂O₃ and PtO_x/ CeO₂-Al₂O₃ at 600°C, water to glycerol ratio of 9:1 and space velocities of 0.25 and 0.5 h⁻¹ as well.

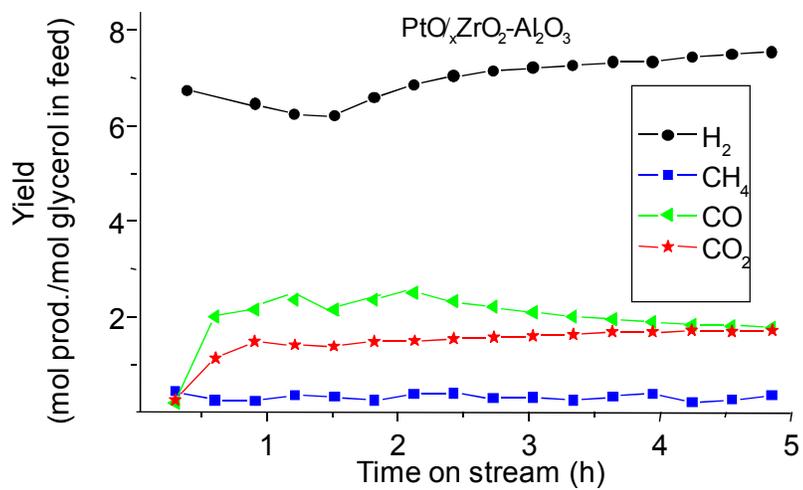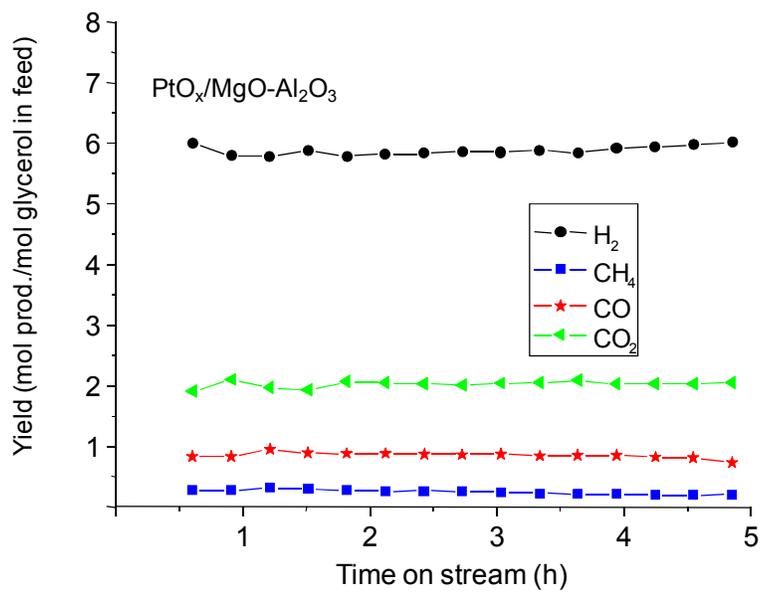


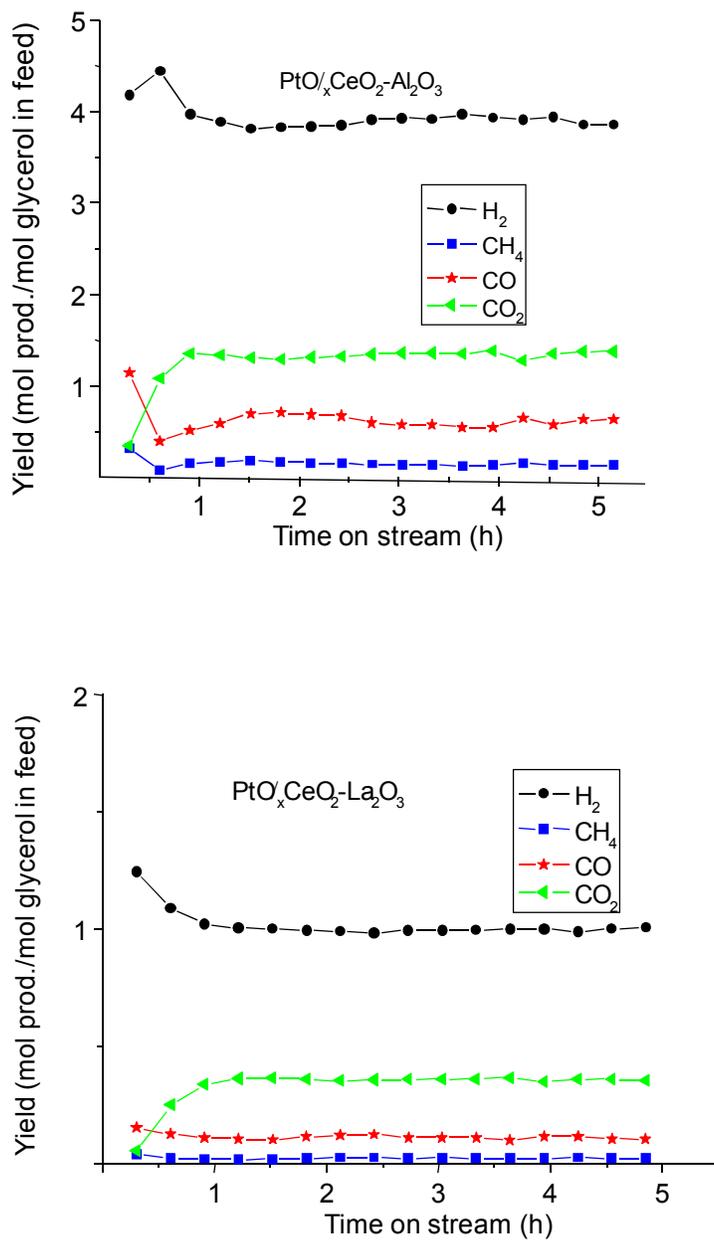


(a)


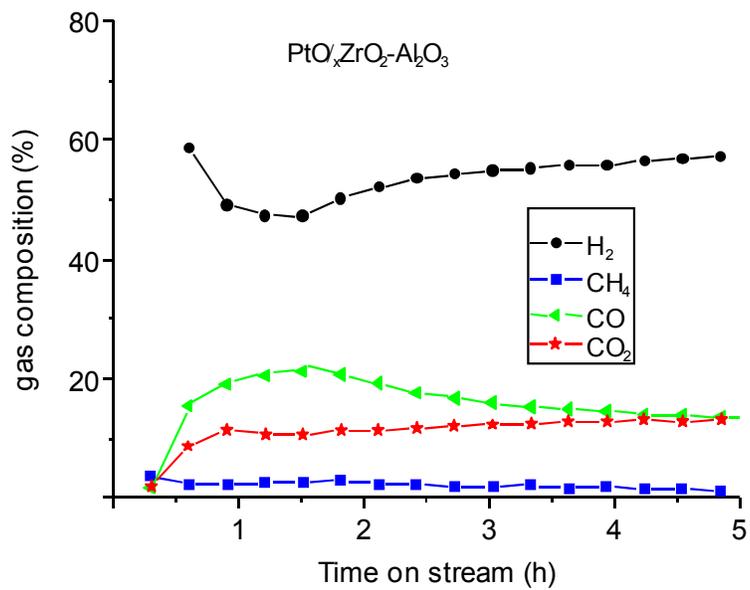


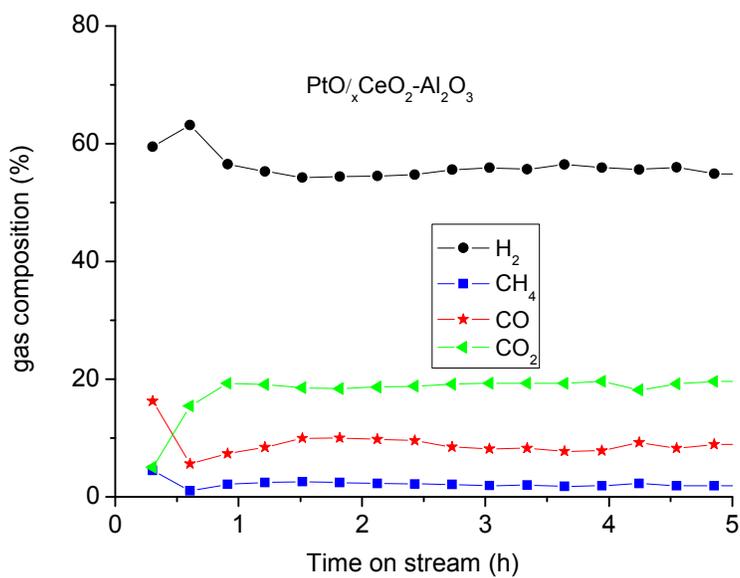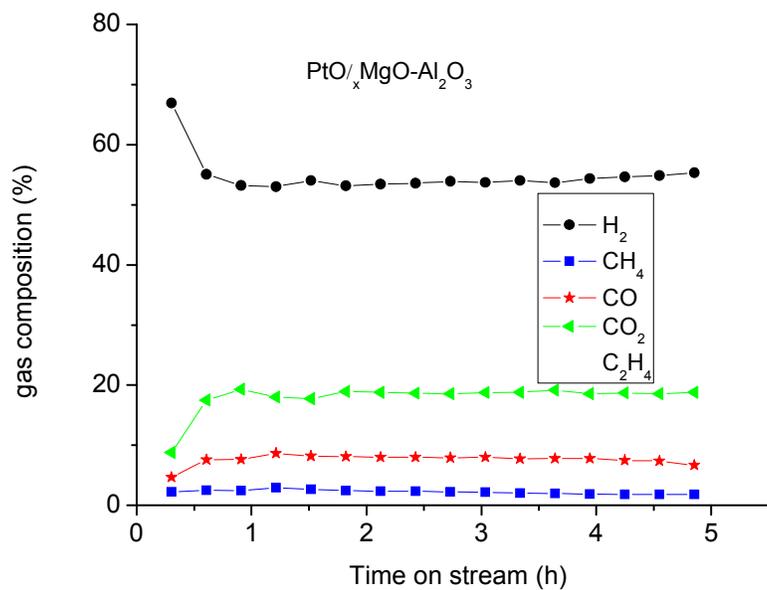


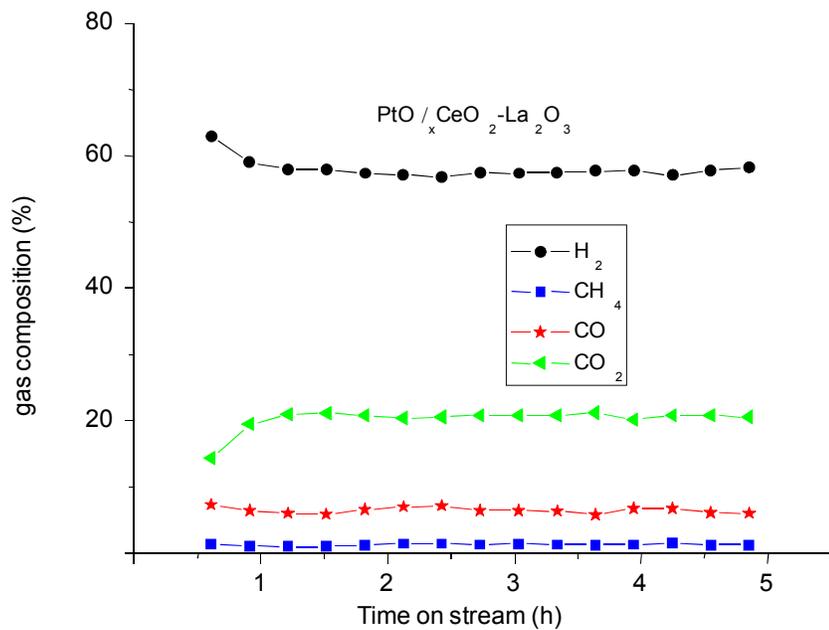



(b)

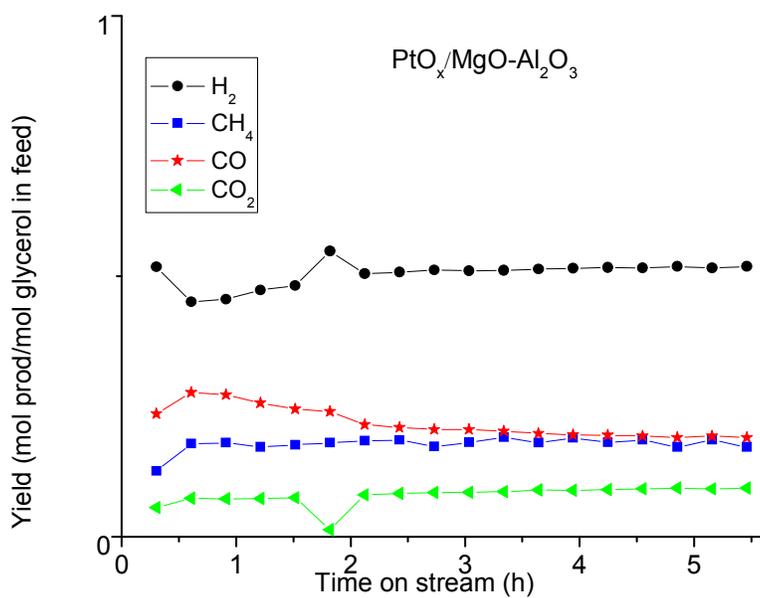


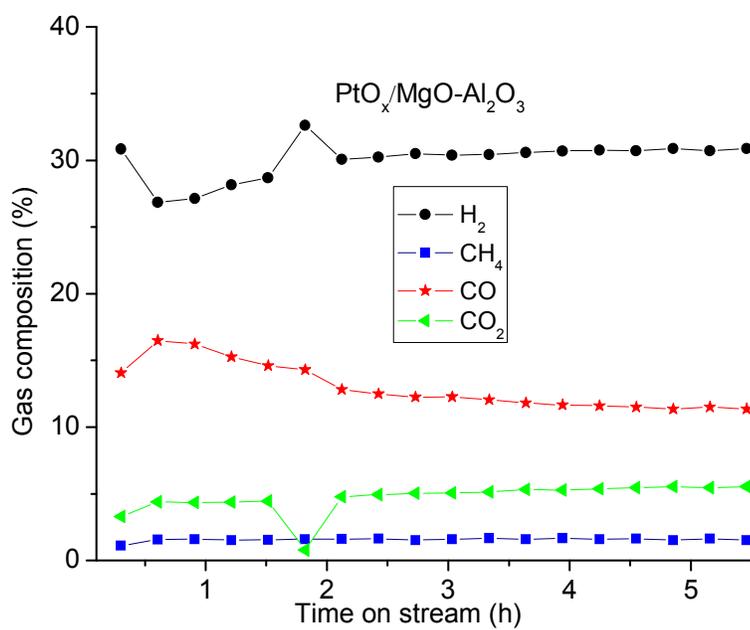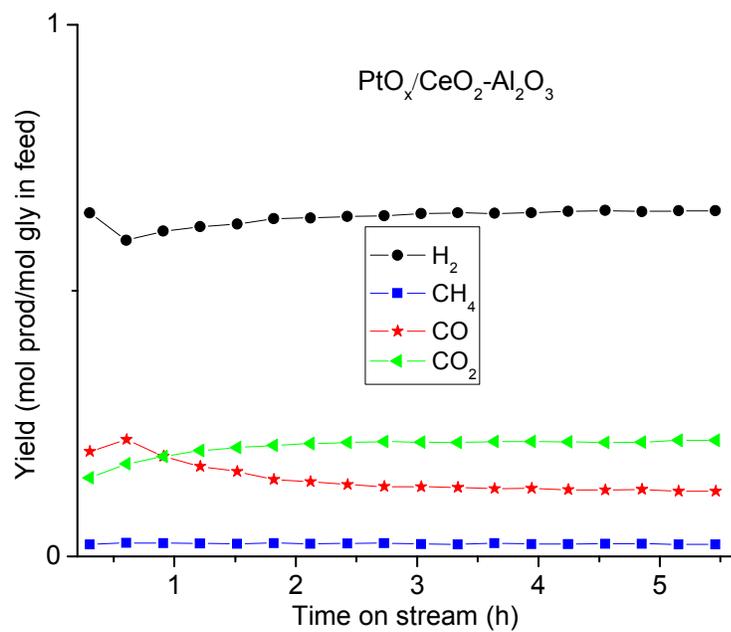

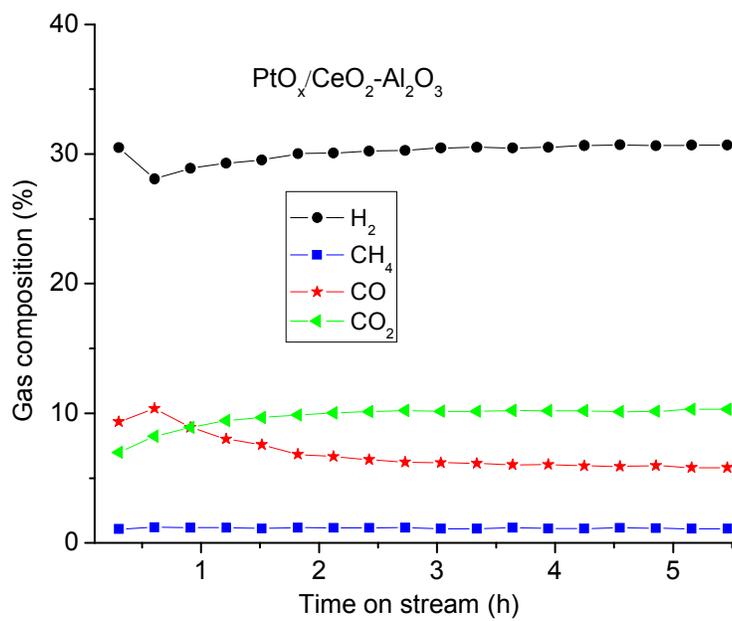

(c)

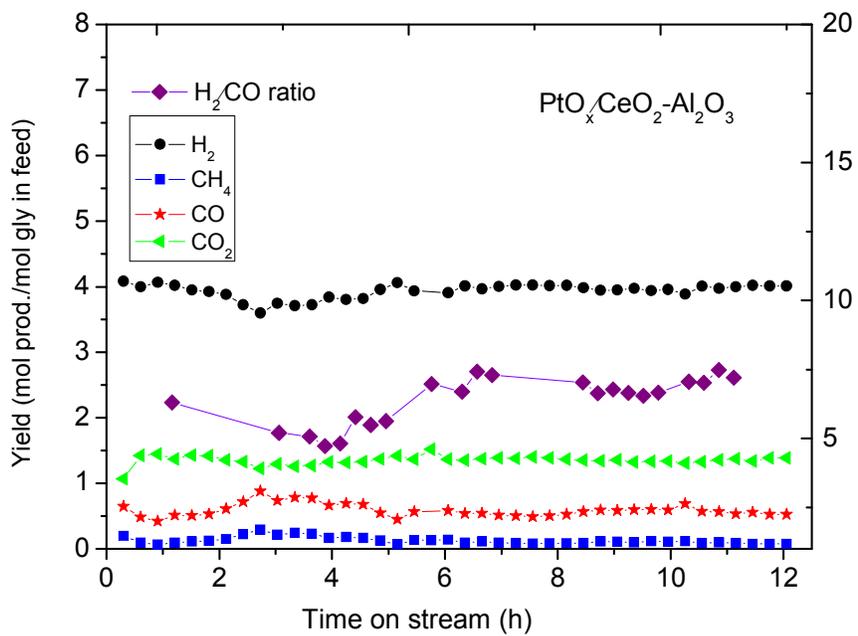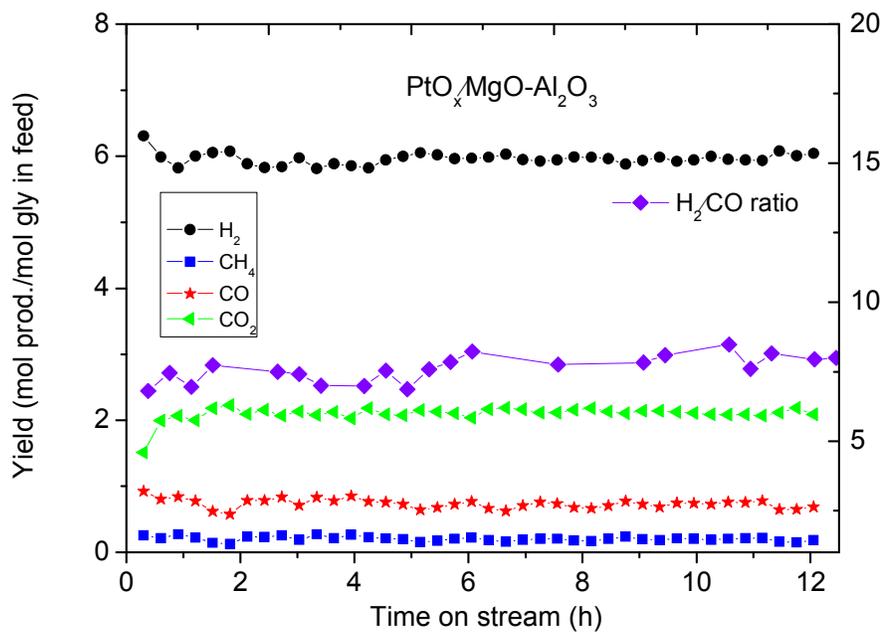

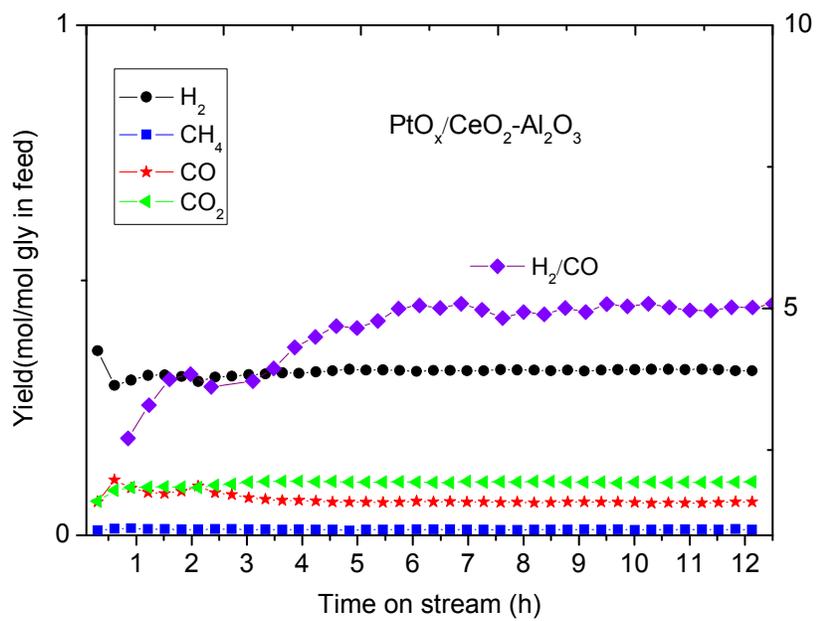

(d)

Fig. 2. XRD patterns of the spent catalysts after 5 h of time on stream in glycerol steam reforming.

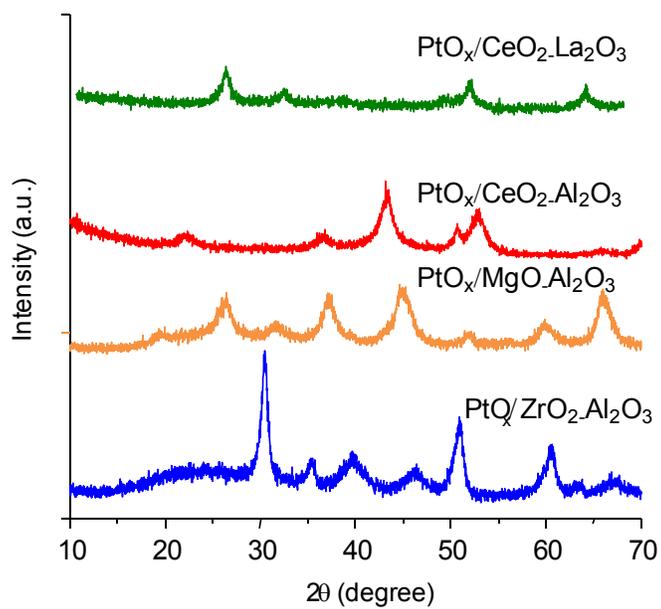


Fig.3. Raman spectra of spent catalysts after 5 h of time on stream. Reaction conditions: fixed temperature (600°C) and water to glycerol ratio of 9.


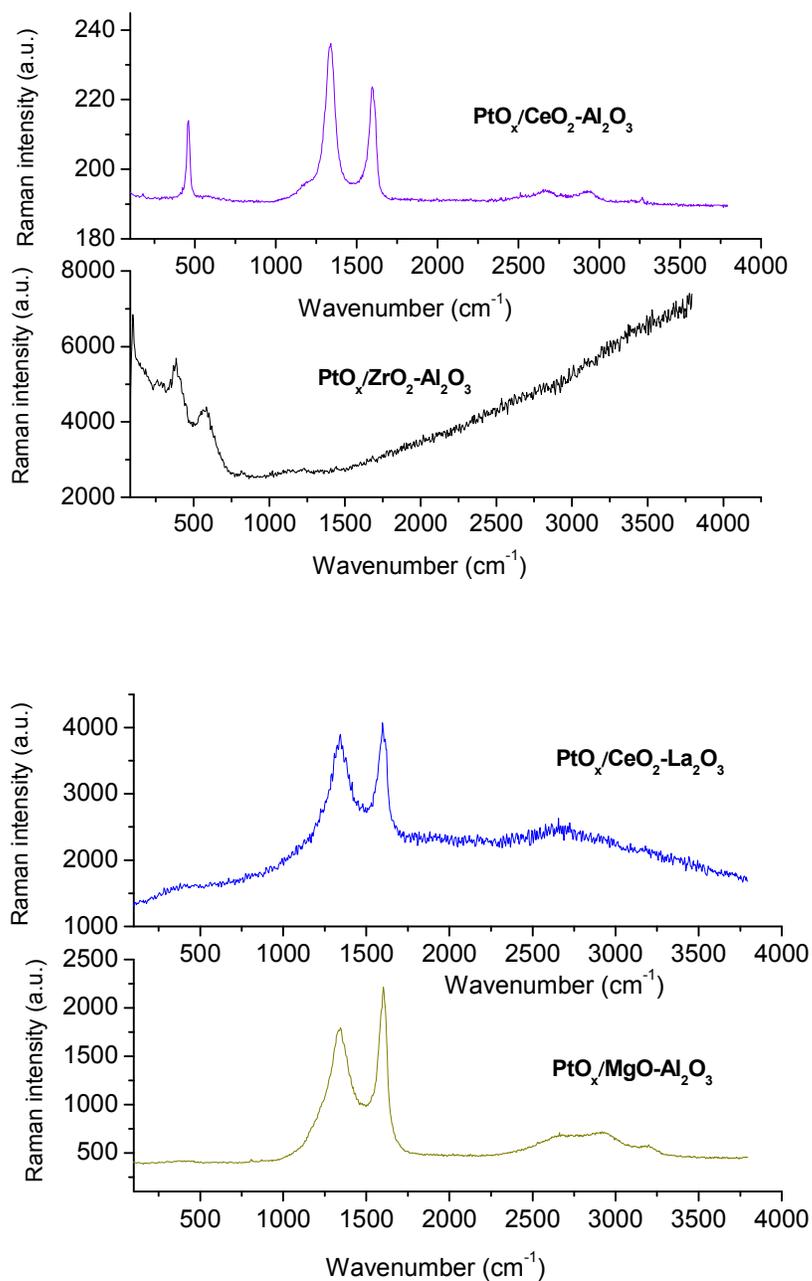



Fig. 4. (a) TEM and HRTEM images of the spent catalysts, after 5 h on stream in SR and water to glycerol molar ratio of 9 at 600 °C.




(a)

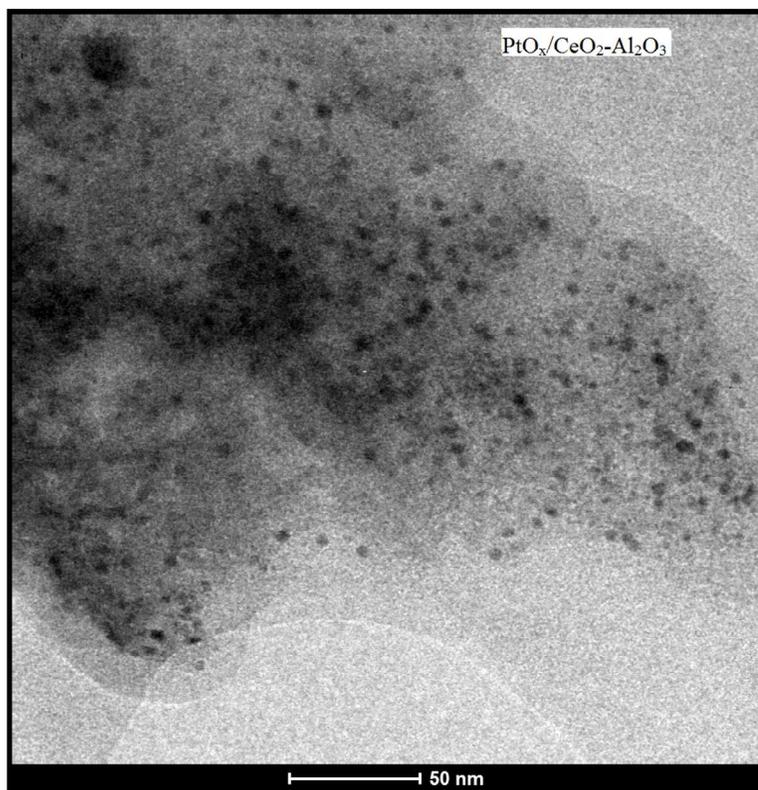



(b₁)

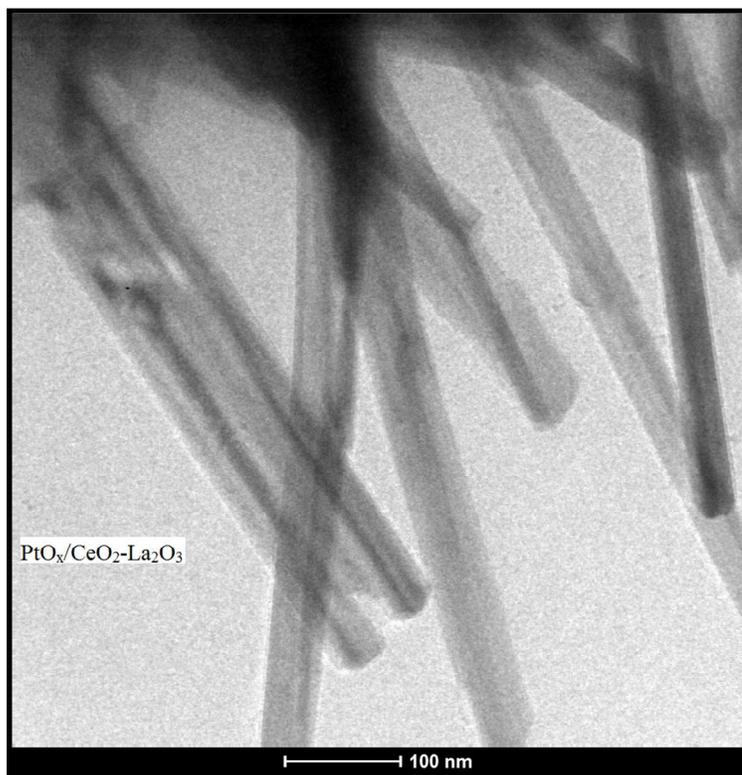(a₂)

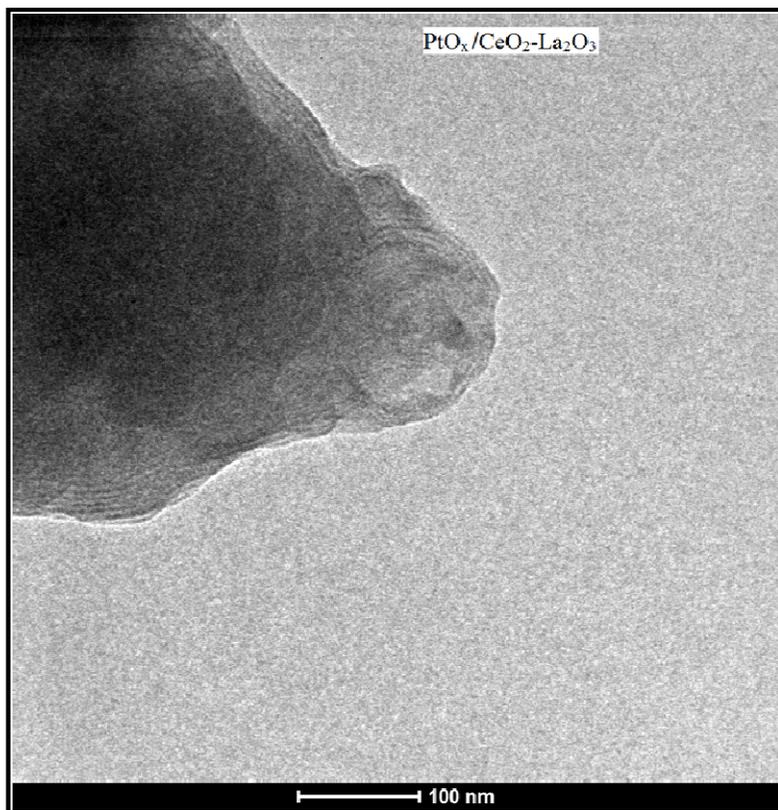


(b₂)

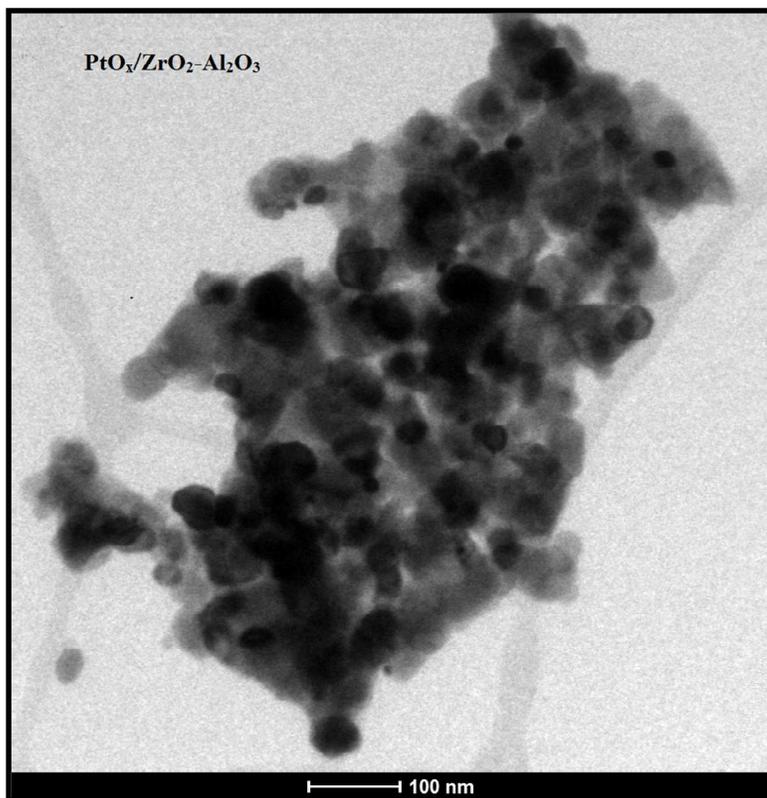
(a₃)

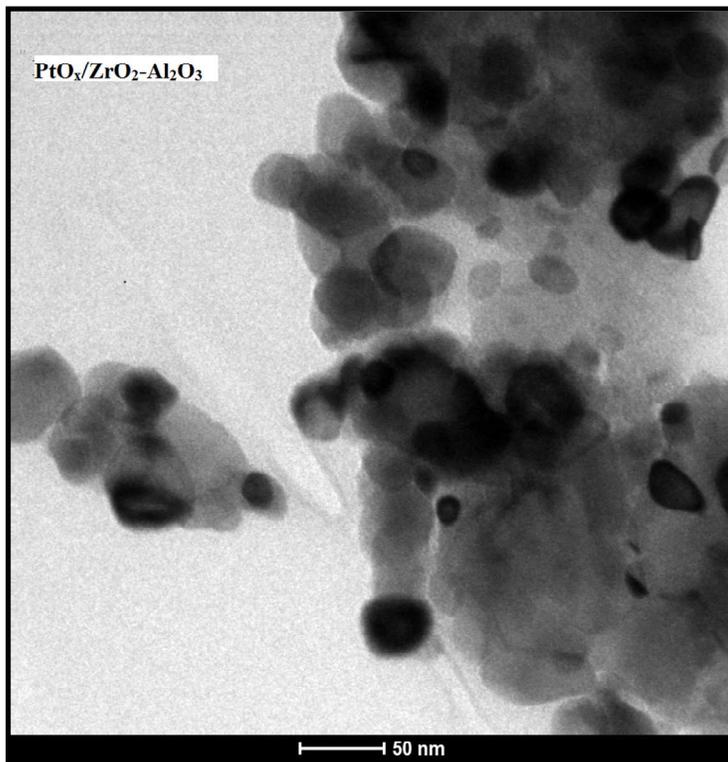

(b₃)

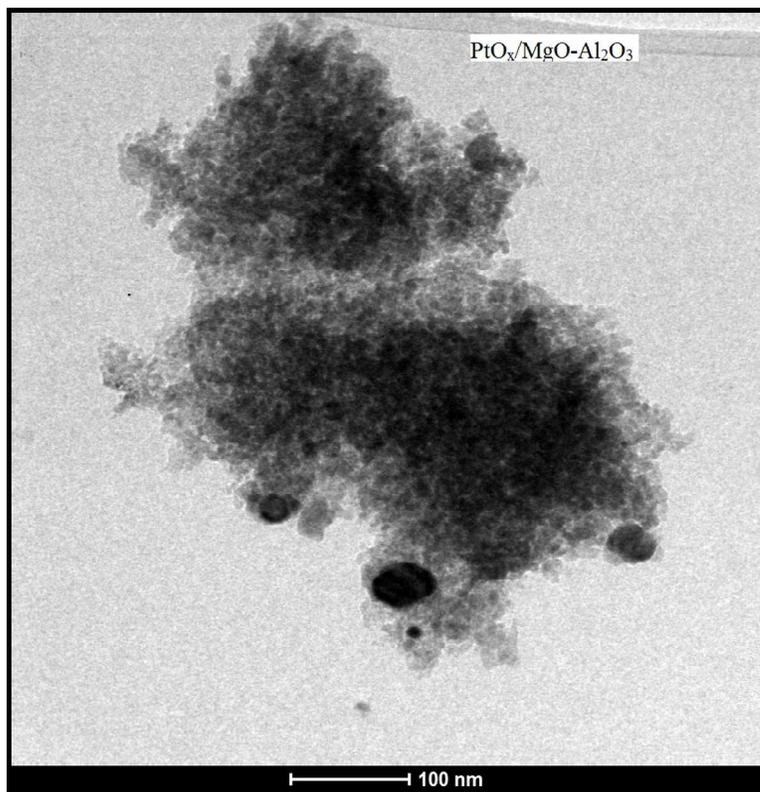


(a)


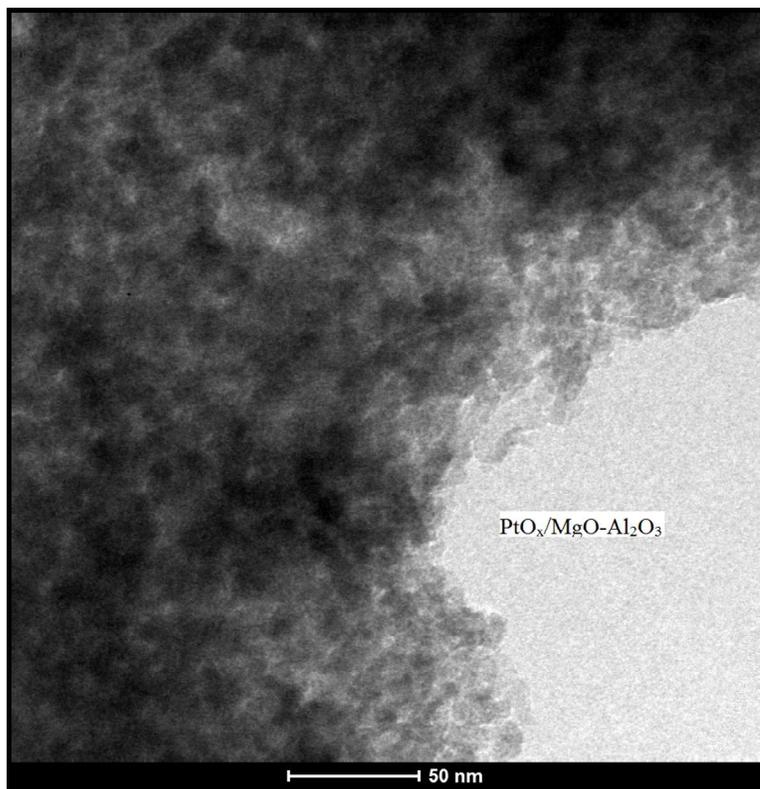




(b₄)


Fig. 5. (a) SEM-EDS of the solids after the catalytic test (b) TG of spent solids.

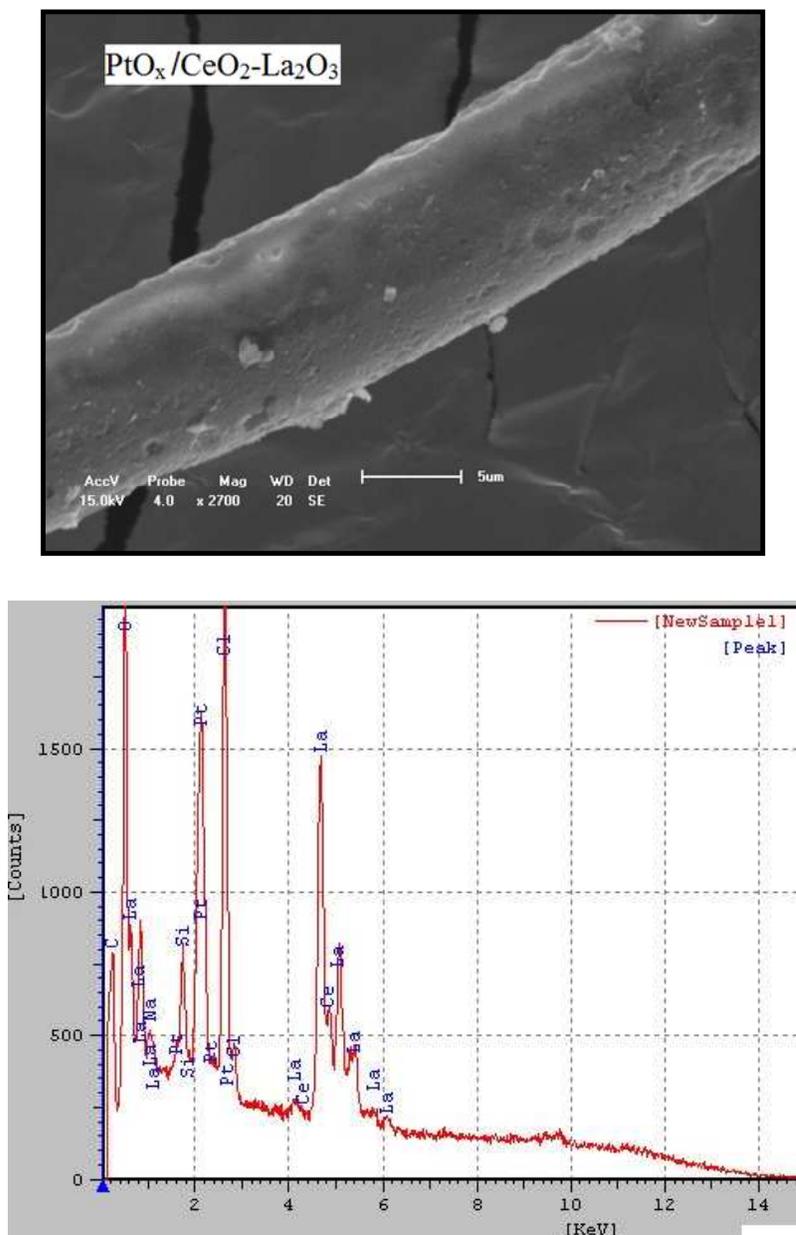


(a₁)

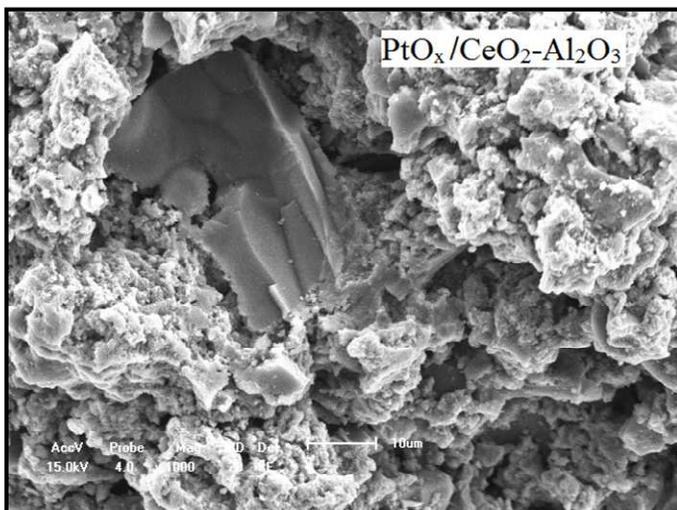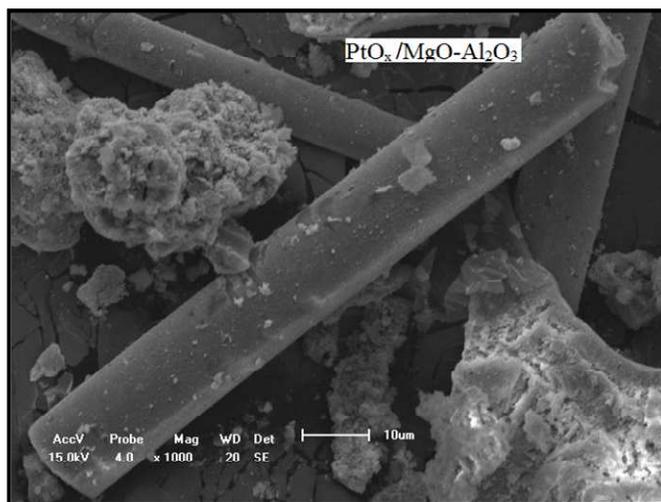(a₂)

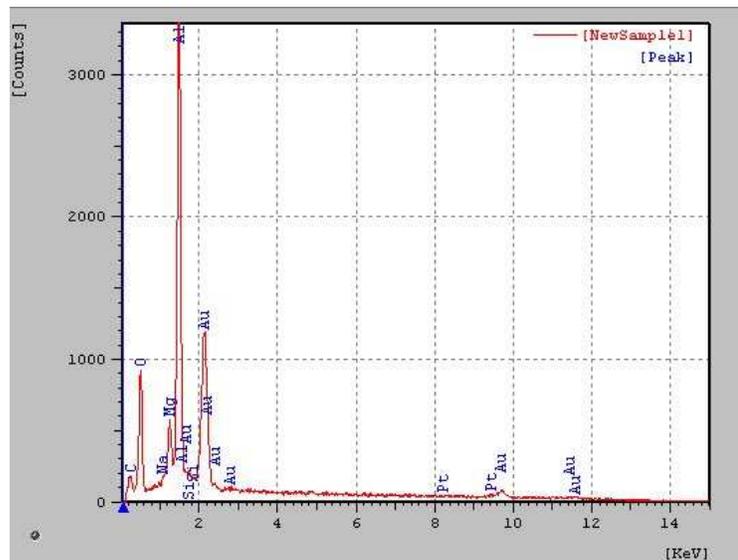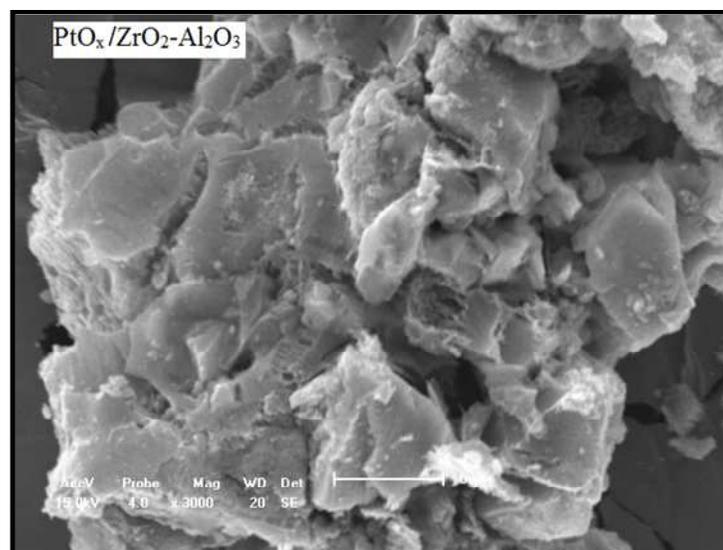(a₃)

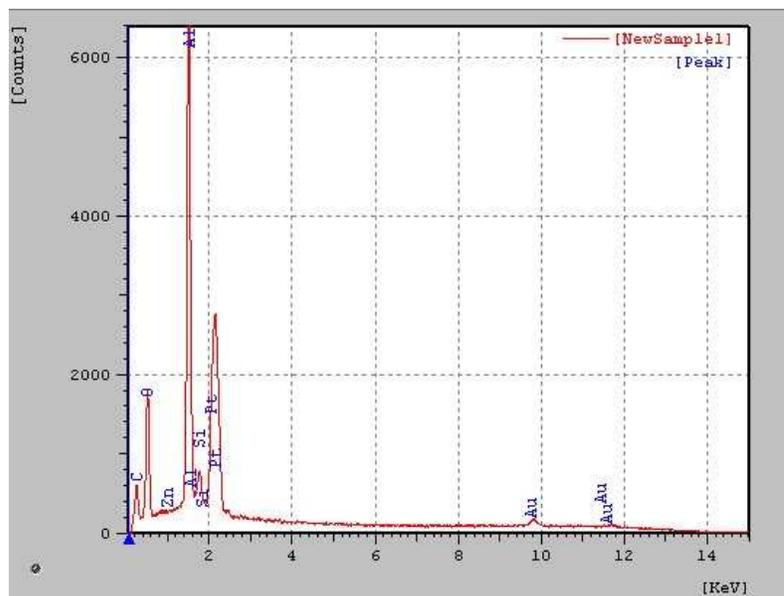(a₄)

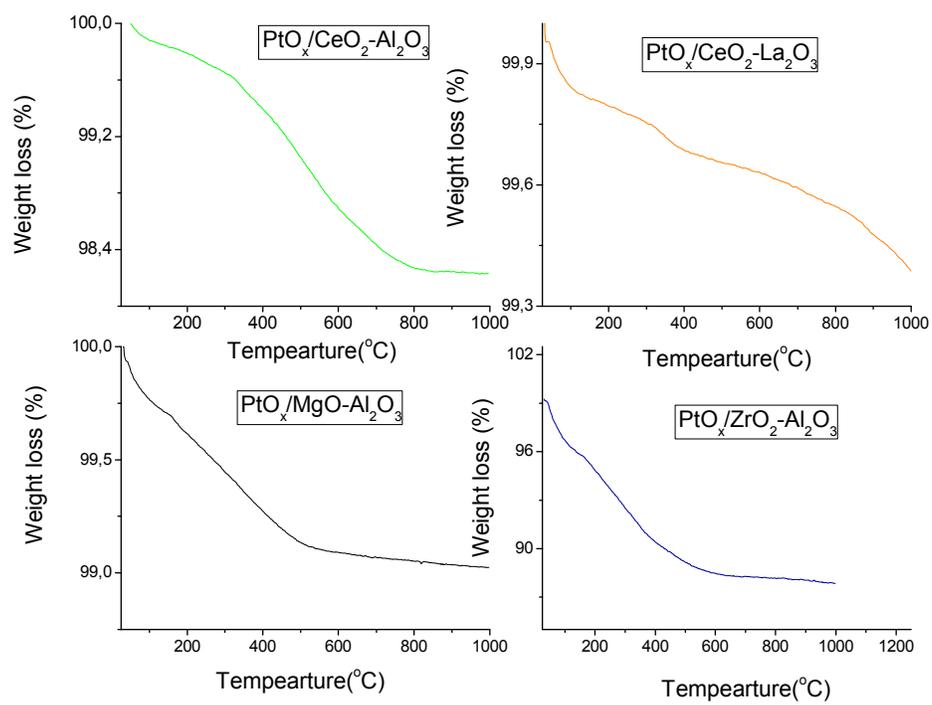

(b)

Tables

Table 1. Catalytic activity of the solids in steam reforming of glycerol reaction. Reaction conditions: reaction temperature at 600 °C, water to glycerol ratio of 9:1 and catalyst mass of 0.10 g during 5 h of reaction. The physicochemical characterizations of the catalysts studied after the aforesaid catalytic test condition.

Catalyst	Glycerol conversion (%)	H ₂ /CO ₂ ratio	H ₂ /CO ratio	Phases detected after the catalytic test	Particle sizes (nm) ^b	S _g ^c (m ² .g ⁻¹)	V _p ^c (cm ³ .g ⁻¹)	D _p ^c (nm)
PtO _x /CeO ₂ -Al ₂ O ₃	97.0	2.8	6.3	CeO ₂ ; γ-Al ₂ O ₃ ; CeAlO ₃ ; C	5	83	0.11	4.5
PtO _x /ZrO ₂ -Al ₂ O ₃	97.0	2.9	5.2	ZrO ₂ ; γ-Al ₂ O ₃	35	73	0.11	2.8
PtO _x /MgO-Al ₂ O ₃	100	2.7	7.5	MgO; γ-Al ₂ O ₃ ; MgAl ₂ O ₄ ; C	15	152	0.20	4.0
PtO _x /CeO ₂ -La ₂ O ₃	96.0	2.6	7.0	CeO ₂ ; γ-Al ₂ O ₃ ; La ₂ O ₃ ; C	30	103	0.14	3.1

^aXRD ^bTEM ^cNitrogen adsorption-desorption measurements

Graphical abstract

