

# Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## ARTICLE

# Heavily Eu<sub>2</sub>O<sub>3</sub>-doped yttria-aluminoborate glasses for red photoconversion with high quantum yield: Luminescence quenching and statistics of cluster formation

Cite this: DOI: 10.1039/x0xx00000x

Guojun Gao<sup>1</sup>, Jingxue Wei<sup>1</sup>, Yang Shen<sup>1</sup>, Mingying Peng<sup>2,3</sup> and Lothar Wondraczek<sup>1,3\*</sup>

Received 13th June 2014,

DOI: 10.1039/x0xx00000x

www.rsc.org/

We report on the photoluminescence (PL) properties of heavily Eu<sub>2</sub>O<sub>3</sub> doped Y<sub>2</sub>O<sub>3</sub>-Al<sub>2</sub>O<sub>3</sub>-B<sub>2</sub>O<sub>3</sub> glasses as a high-gain red-emitting material for photoconversion. A UV-to-red conversion efficiency of up to 60 % is achieved in this material. Concentration quenching is related to the formation of -{Eu-O-Me-O-Eu}- (Me = B, Y, Al) and -{Eu-O-Eu}- linkages in the first and second coordination shell, respectively, of Eu<sup>3+</sup>. For a quantitative consideration, we employ a statistical approach to estimate the number of those species as a function of europium concentration. In this way, a crossover composition is obtained at a dopant concentration of ~ 3 mol % of Eu<sub>2</sub>O<sub>3</sub> where further addition of europium directly increases the number of -{Eu-O-Eu}-. In the latter species, the critical distance for concentration quenching of PL is achieved so that for concentrations above the crossover, PL quantum efficiency decreases. This observation is confirmed experimentally through lifetime analyses as well as direct measurements of internal quantum efficiency. The proposed tool can now be used to predict and optimize cluster formation and concentration quenching in rare-earth doped glasses.

## Introduction

Inorganic materials doped with trivalent europium have been of strong interest for photo-conversion due to the 4f<sup>6</sup> electronic configuration of Eu<sup>3+</sup> which results in the characteristic red photoluminescence (PL) with often high quantum efficiency.<sup>1</sup> In detail, the PL spectrum of Eu<sup>3+</sup> usually exhibits a variety of sharp PL lines in the orange to red spectral region arising from the intra-configurational parity-forbidden 4f<sup>6</sup> → 4f<sup>6</sup> electronic transitions from the non-degenerated <sup>5</sup>D<sub>0</sub> level to the ground levels of <sup>7</sup>F<sub>J</sub> (J = 0, 1, 2, 3 and 4).<sup>1-4</sup> While the band energy of these f-f transitions is usually not dependent on ligand field strength and, hence, the host material, the electric-dipole allowed transition of Eu<sup>3+</sup>:<sup>5</sup>D<sub>0</sub> → <sup>7</sup>F<sub>2</sub> depends strongly on local symmetry. As a consequence, this transition can be used to probe local structure in the considered host material. For this, the relative PL intensity ratio *R* of the electric- and magnetic-dipole-allowed transitions (usually denoted *asymmetry ratio*) is calculated,  $R = I_{ED}/I_{MD}$ . For example, a high value of *R* reflects low ligand symmetry and high bond covalency of the Eu<sup>3+</sup> species.<sup>5-7</sup> The intrinsic excitation bands of Eu<sup>3+</sup> are located in the near-ultraviolet spectral range (NUV), i.e., between ~ 360 to 420 nm, and in the blue (~ 464 nm). However, the parity-forbidden nature of Eu<sup>3+</sup> absorption results in only low absorption cross section. Enhancing the Eu<sup>3+</sup> doping concentration in the host material is one way to overcome this problem, but only as far as concentration quenching of photoluminescence can be avoided. This results in a trade-off between absorption efficiency, quantum efficiency and re-absorption.<sup>8</sup> In particular, glasses with high quantum yield of

photoluminescence are desirable for applications where high transparency for light other than the excitation light is required to enable visually transparent emitters.<sup>8</sup> Such target applications are, for example, luminescent concentrators<sup>9-11</sup>, bulk spectral converters for photochemical<sup>12</sup> or photovoltaic solar energy harvesting<sup>13,14</sup>, or three-dimensional luminescent displays<sup>15</sup>. Compared to (single-) crystalline hosts, glasses provide the major advantage of facile processing into almost any size and shape.

In the present study, we consider the borate system of Y<sub>2</sub>O<sub>3</sub>-Al<sub>2</sub>O<sub>3</sub>-B<sub>2</sub>O<sub>3</sub> (YAB).<sup>16</sup> On the one hand, borate glasses generally offer a comparably high solubility for rare-earth ions.<sup>8,17</sup> In addition to this, the crystalline YAl<sub>3</sub>(BO<sub>3</sub>)<sub>4</sub> is known as an excellent nonlinear optical crystal and host for various rare-earth dopants (e.g., Nd<sup>3+</sup> and Yb<sup>3+</sup>).<sup>18,19</sup> However, especially the incongruent melting of the constituting oxides strongly complicates the synthesis of single-crystalline YAl<sub>3</sub>(BO<sub>3</sub>)<sub>4</sub>, which puts a limit on possible applications. On the other hand, due to the similarity of ionic radii (0.90 vs. 0.947 Å), the octahedral site of Y<sup>3+</sup> can readily be occupied by Eu<sup>3+</sup>.<sup>20</sup> While there is no clear data available, in the glassy matrix, we expect a 6 to 8-fold coordination situation for both Y<sup>3+</sup> and Eu<sup>3+</sup>, with a tendency to lower coordination with higher Y/Eu content.<sup>21,22</sup> Due to the supposedly less symmetric environment of the Y<sup>3+</sup>/Eu<sup>3+</sup>-sites, however, we also expect that the red emission band at ~ 612 nm will be more dominant in the PL spectrum of Eu<sup>3+</sup>-doped yttria-aluminoborate glasses.<sup>23-25</sup> Finally, rare earth species (e.g., Eu<sup>3+</sup>) tend to be better dispersed in glasses as compared to crystals, which may be advantageous with respect to dopant concentration and concentration quenching of PL.<sup>26</sup>

## Experimental Section

Precursor glasses were chosen at an excess of  $B_2O_3$  versus  $(Eu,Y,Al)_2O_3$  as compared to the stoichiometric  $YAl_3(BO_3)_4$ , and also at an excess of  $(Eu^{3+}, Y^{3+})$  over the  $Al^{3+}$ -ion with higher-field strength in order to ensure facile glass formation and high rare-earth content. Nominal compositions (mol%) were  $(20-x)Y_2O_3-20Al_2O_3-60B_2O_3-xEu_2O_3$  (YAB- $x$ Eu with  $x=0, 0.25, 0.5, 1, 2, 4, 8$  and  $20$ ). Corresponding mixtures of  $Y_2O_3$  (99.99%),  $Al_2O_3$  (99.9%),  $H_3BO_3$  (99.9%) and  $Eu_2O_3$  (99.999%) were prepared in batches of  $\sim 30$  g and melted conventionally in alumina crucibles at  $1400$  °C for 2 h in air. Melts were poured into preheated stainless steel moulds and annealed at  $600$  °C for 2 h to obtain stress-free glass slabs. These were subsequently cut into disks of  $\sim 30 \times 20 \times 5$  mm<sup>3</sup> and polished on both sides for further characterization.

UV-vis absorption spectra were recorded with a double-beam photospectrometer (Cary 5000) over the spectral range of 300 to 700 nm with a step size of 1 nm. Static photoexcitation (PLE) and luminescence (PL) spectra and dynamic decay curves of  $Eu^{3+}$ -related PL were collected with a high-resolution spectrofluorometer (Horiba Jobin Yvon Fluorolog FL3-22). PLE spectra were corrected over the lamp intensity with a silicon photodiode. PL spectra were corrected by the spectral response of employed photomultiplier tube. Absorbance, internal ( $\eta_{IQE}$ ) and external quantum efficiency ( $\eta_{EQE}$ ) were obtained through measuring excitation and emission spectra on samples and a blank reference with a  $BaSO_4$ -coated integration sphere. The values of absorbance ( $a$ ),  $\eta_{IQE}$  and  $\eta_{EQE}$  were then determined as follows:

$$a = \left( \int E_R - \int E_S \right) / \int E_R \quad (1)$$

$$\eta_{IQE} = \left( \int L_S - \int L_R \right) / \left( \int E_R - \int E_S \right) \quad (2)$$

$$\eta_{EQE} = \eta_{IQE} \cdot a \quad (3)$$

In Equ. 1-3,  $\int L_S$  and  $\int L_R$  are the integrated PL intensities with and without the sample, and  $\int E_R$  and  $\int E_S$  are the integrated intensities of excitation light without and with the sample in the integration sphere, respectively. CIE 1931 (Commission International de l'Eclairage) chromaticity coordinates were determined by integrating the PL spectra. All analyses were performed at room temperature.

## Results and discussion

Figure 1a shows the UV-vis optical absorption spectra of YAB- $x$ Eu glasses for various concentrations of  $Eu_2O_3$ . For  $Eu^{3+}$ -doped samples, seven characteristic absorption bands of  $Eu^{3+}$  with maxima at 362, 376, 394, 414, 465, 532 and 579 nm arising from the intrinsic  $4f \leftrightarrow 4f$  transitions of  $Eu^{3+}$  from the ground state  ${}^7F_0$  to the labeled excited states can be identified, as illustrated schematically in the energy level diagram of  $Eu^{3+}$  (inset of Fig. 1a).<sup>8,26,27</sup> The increased intensity of absorption bands of  $Eu^{3+}$  with  $Eu_2O_3$  concentration especially in the UV region results in a shift of the absorption edge to longer wavelength, which is reflected by the changing visual color of the samples from colorless to dark orange with increasing  $Eu_2O_3$  concentration (Fig. 1e). Figures 1b-c present PLE spectra of YAB- $x$ Eu glasses by monitoring  $Eu^{3+}$  PL at 612 nm. In full agreement with the absorption bands of  $Eu^{3+}$  (Fig. 1a), six typical PLE lines of  $Eu^{3+}$  peaking at 318, 362, 376, 394, 414 and 464 nm are observed. They are assigned to the aforementioned transitions of  $Eu^{3+}$  from the ground state  ${}^7F_0$  to the labeled excited states (Fig. 1b).<sup>25</sup> The sharp PLE line at 394 nm ( $Eu^{3+}: {}^7F_0 \rightarrow {}^5L_6$ ) which shows the strongest intensity is chosen as PLE wavelength to record the following PL spectra (Fig. 1c).

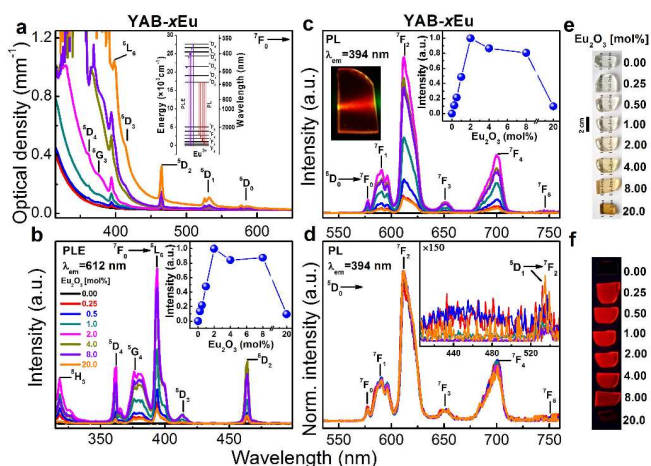


Figure 1. (a) UV-vis absorption spectra of YAB- $x$ Eu glasses as a function of  $Eu_2O_3$  doping concentration. Room temperature (b) PLE ( $\lambda_{em}=612$  nm), (c) PL ( $\lambda_{ex}=394$  nm) and (d) normalized PL ( $\lambda_{ex}=394$  nm; normalized to the PL peak at 612 nm) spectra of YAB- $x$ Eu dependent on  $Eu_2O_3$  doping concentration (labels: doping concentration of  $Eu_2O_3$  in mol%). (e-f): Photographs of YAB- $x$ Eu glasses in sunlight (e) and under UV-A irradiation (f). The inset of (a) shows the energy levels of  $Eu^{3+}$ . Inset of (b) and (c) show the PL peak intensity at 612 nm and PLE peak intensity at 394 nm of  $Eu^{3+}$  versus doping concentration of  $Eu_2O_3$ , respectively. The inset in (c) is a photograph of YAB-8Eu under irradiation with a 532 nm laser diode. Inset of (d): Zoom at spectral region of 400 to 550 nm. The drawn lines in the inset of (b) and (c) are guides for the eye.

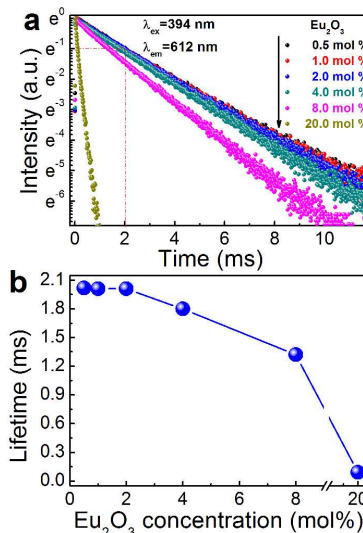


Figure 2. (a) Decay kinetics of the  $Eu^{3+}: {}^5D_0 \rightarrow {}^7F_2$  emission at 612 nm as a function of  $Eu_2O_3$  doping concentration under excitation at 394 nm. (b) Variation of the effective lifetime  $\tau_{1/e}$  ( $\lambda_{em}=612$  nm and  $\lambda_{ex}=394$  nm) as a function of doping concentration.

Six characteristic PL lines of  $Eu^{3+}$  peaking at 578, 591, 612, 652, 700 and 748 nm are observed. These bands are attributed to the  $4f^6 \leftrightarrow 4f^6$  transitions of  $Eu^{3+}$  from the lowest excited state  ${}^5D_0$  to the ground state multiplet of  ${}^7F_J$  ( $J=0, 1, 2, 3, 4$  and  $5$ ).<sup>25</sup> The intensity of all  $Eu^{3+}$  PL lines increases linearly with increasing  $Eu_2O_3$  concentration up to  $x = 2$ . A plateau is found for further increasing concentration up to  $x \leq 8$  mol%, reflecting the interplay of the negative effect of beginning concentration quenching and the positive effect of further

increasing absorbance on PL intensity. Strong quenching is found for the sample doped with 20 mol%  $\text{Eu}_2\text{O}_3$ . This observation is confirmed through dynamic PL analyses. The decay curves of  $\text{Eu}^{3+}$  PL (at 612 nm) follow a single-exponential function for all studied dopant concentrations. The effective emission lifetime  $\tau_{1/e}$  of  $\text{Eu}^{3+}$  remains at a constant value of  $\sim 1.90$  ms up to  $x = 2$ . For higher doping concentration up to  $x = 8$ , it decreases to  $\sim 1.35$  ms, and decreases more for  $x = 20$ , i.e., to  $\sim 0.092$  ms (Fig. 2a). This indicates that concentration quenching sets-in at a concentration of  $\sim x = 2$ : at this concentration, the distance between neighbouring  $\text{Eu}^{3+}$ -species becomes critical so that energy transfer and non-radiative relaxation may occur. As previously noted, unfortunately, clear data on  $\text{Eu}^{3+}$  (or  $\text{Y}^{3+}$ ) coordination in the considered glass is not available. For a first approximation, we may assume two principle coordination environments, i.e., 6-fold and 8-fold which are typically found for  $\text{Eu}^{3+}$  in oxide glasses.<sup>22,28,29</sup>

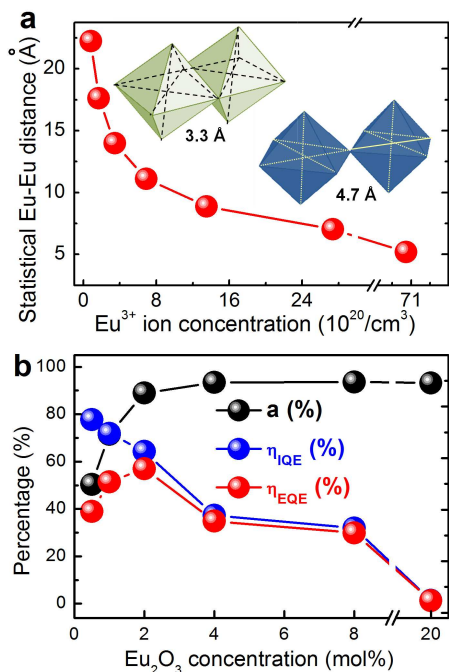


Figure 3. (a) Average statistical  $\text{Eu}^{3+}$ - $\text{Eu}^{3+}$  distance as a function of volumetric ion concentration of  $\text{Eu}^{3+}$ . The inset of (a) exemplarily shows edge and corner-sharing octahedral  $[\text{EuO}_6]$  species through a linear Eu-O-Eu group. The labels indicate the corresponding minimum Eu-Eu-distance. (b) Variation of absorbance (a), internal quantum efficiency ( $\eta_{IQE}$ ) and external quantum efficiency ( $\eta_{EQE}$ ) of red PL of  $\text{Eu}^{3+}$  under excitation at 394 nm in YAB-xEu glasses versus doping concentration of  $\text{Eu}_2\text{O}_3$ . The drawn lines in the inset of (a) and (b) are to guide the eye.

At room pressure, the minimum Eu-Eu-distance for corner-sharing polyhedra through a linear Eu-O-Eu group corresponds to twice the Eu-O-distance which is about 2.34 Å in  $\text{Eu}_2\text{O}_3$ , i.e.,  $\sim 4.7$  Å. For edge-sharing, it is  $\sim 3.3$  Å (inset of Fig. 3a). A somewhat higher Eu-O distance would occur in 8-fold oxygen coordinated  $\text{Eu}^{3+}$ , i.e.,  $\sim 2.4$  Å, corresponding to  $\sim 4.8$  and  $\sim 3.4$  Å for corner and edge-sharing groups, respectively.<sup>22</sup> A first estimate of the average statistical distance between all  $\text{Eu}^{3+}$  species can be obtained directly from the volumetric ion concentration. This is illustrated in Fig. 3a. In this consideration, the critical average Eu-Eu distance at which the onset of notable concentration quenching is observed corresponds  $\sim 11.1$  Å for  $x=2$ . Even though we are considering a glassy lattice, however, it is clear that within the length scale regime of  $< 20$  Å, the average value of interionic distances has only little meaning because the mid-

and short-range structure is more and more specified. That is, within the first and second coordination shell, the distribution of potential Eu-Eu distances converges around two values which correspond to the bridging species of  $-\{\text{Eu-O-Eu}\}$ - (first coordination shell, Fig. 4b) and  $-\{\text{Eu-O-Me-O-Eu}\}$ - (second coordination shell, Fig. 4a, with Me = B, Y, Al according to the chemical composition of the considered glass). If we neglect the potential impact of local chemical heterogeneity (preferential ion clustering, dynamic heterogeneity, etc.), the speciation into either of the two configurations is given by the probability at which they occur in the glass lattice. For the  $-\{\text{Eu-O-Eu}\}$ - species, this probability is approximately

$$P_{\text{Eu-Eu}} = 1 - (1 - x/100)^{\text{CN}_{\text{Eu}}} \quad (4)$$

, with the Eu-coordination number  $\text{CN}_{\text{Eu}}$  and assuming an infinitely large ensemble of atoms. For the  $-\{\text{Eu-O-Me-O-Eu}\}$ - species, i.e., for having no Eu-neighbour on the first coordination shell but one on the second, it is

$$P_{\text{Eu-Me-Eu}} = (1 - P_{\text{Eu-Eu}}) \cdot (1 - (1 - x/100)^{\text{CN}_{\text{Av}} - 1})^{\text{CN}_{\text{Eu}}} \quad (5)$$

In Eq. 5,  $\text{CN}_{\text{Av}}$  is the average coordination number of the cation species on the first coordination shell. As an approximation, we use  $^{\text{IV}}\text{B}$ ,  $^{\text{VI}}\text{Al}$  and  $^{\text{VI}}\text{Y}$  and average according to the glass composition and the value of  $x$ . The result of this calculation is shown in Fig. 4c. As the accurate average coordination number of  $\text{Eu}^{3+}$  is not known for the present glass system beyond that it lies between six and eight, we plot data for  $^{\text{VI}}\text{Eu}$  and  $^{\text{VIII}}\text{Eu}$ . We also plot the sum of  $P_{\text{Eu-Eu}}$  and  $P_{\text{Eu-Me-Eu}}$  as a measure of at least how many of the Eu species are found within the first or second coordination shells of each other. That is, when this sum approaches unity, each Eu has at least one other Eu within its first or second coordination shell. At the nominal  $\text{Eu}_2\text{O}_3$  dopant concentration of  $\sim 3$  mol%, we find a compositional crossover where the statistical number of  $-\{\text{Eu-O-Me-O-Eu}\}$ -species starts to decrease in favour of  $-\{\text{Eu-O-Eu}\}$ -. Interestingly, this crossover composition corresponds well to the observed onset of notable concentration quenching. At the crossover point, we may assume that about 60 % of the Eu species lie within  $\sim 10$  Å of each other, and about 25 % are first-shell neighbours which lie within  $\sim 4.7$  Å of each other.

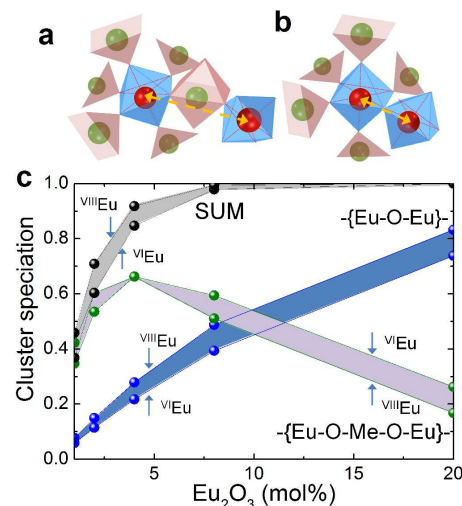


Figure 4. (a-b) Schematic illustration of the  $-\{\text{Eu-O-Eu}\}$ - and  $-\{\text{Eu-O-Me-O-Eu}\}$  (Me = B, Y, Al) linkages in the first and second coordination shell, respectively, of the  $\text{Eu}^{3+}$  ion. (c) Probability of cluster speciation  $P_{\text{Eu-Eu}}$  and  $P_{\text{Eu-Me-Eu}}$ , and sum of ( $P_{\text{Eu-Eu}} + P_{\text{Eu-Me-Eu}}$ ), calculated for the two extremes of coordination number (six- and eight) as a function of  $\text{Eu}_2\text{O}_3$  concentration. The drawn lines in (c) are to guide the eye.



This observed correlation confirms that the Eu-Eu linkages form mostly statistically with no notable contribution of selective cluster formation or even phase separation. At the crossover composition, newly added  $\text{Eu}_2\text{O}_3$  does not anymore contribute to the number of -{Eu-O-Me-O-Eu}- or farther separated Eu species which act as efficient luminescence centers. Instead, from this composition onwards, every Eu-ion which is added to the material increases the number of -{Eu-O-Eu}- in which the critical interaction distance for PL quenching is achieved. Hence, notable PL quenching is observed for higher dopant concentrations. We believe that this approach can be used to predict and optimize the concentration quenching properties of similar photoluminescent glasses.

As expected, the PL spectra are dominated by the electronic-dipole allowed transition of  $\text{Eu}^{3+}:^5\text{D}_0 \rightarrow ^7\text{F}_2$  at 612 nm for all samples which suggests an environment of lower symmetry for the  $\text{Eu}^{3+}$  species. As already noted, the intensity of the electronic-dipole allowed transition is strongly dependent on the symmetry of the local environment while the magnetic-dipole allowed transition of  $\text{Eu}^{3+}:^5\text{D}_0 \rightarrow ^7\text{F}_1$  is independent of symmetry. Here, we obtain an asymmetry ratio of  $R \sim 3.55$ , which is a relatively high value.<sup>5-8</sup> This confirms the distortion of local symmetry in YAB glasses. Expectedly,  $R$  does not notably depend on  $\text{Eu}^{3+}$  concentration  $x$ , which reflects the very similar structural role of  $\text{Y}^{3+}$  and  $\text{Eu}^{3+}$ .<sup>30,31</sup>

As already noted, there is no notable variation in the intensity ratios of all emission peaks. The corresponding CIE 1931 chromaticity coordinates of all sample are ( $\sim 0.650 \pm 0.003$ ,  $\sim 0.349 \pm 0.001$ ), close to the NTSC standard red of (0.670, 0.330). For illustration, we show photographs of the samples UV-A light (Fig. 1f) and under local excitation with a green laser beam (532 nm, Fig. 1c). Besides the PL lines from the lowest excited state of  $\text{Eu}^{3+}:^5\text{D}_0$ , the PL lines which originate from higher lying levels such as  $^5\text{D}_1$  are very weak or even absent in all samples (inset of Fig. 1d). This is due to the relatively high maximum phonon energy of the considered borate glass system ( $\sim 1400 \text{ cm}^{-1}$ ).<sup>32-34</sup> The forbidden transition of  $\text{Eu}^{3+}:^5\text{D}_0 \rightarrow ^7\text{F}_0$  at 580 nm can be observed in all samples. Noteworthy,  $\text{Eu}^{2+}$ -related photoluminescence cannot be observed in any of the samples.

The absorbance ( $a$ ), internal quantum efficiency ( $\eta_{\text{IQE}}$ ) and external quantum efficiency ( $\eta_{\text{EQE}}$ ) are reported in Fig. 3b. For  $x = 0.5 \text{ mol}\%$ , we obtain a value of  $\eta_{\text{IQE}}$  of  $\sim 80\%$ . In correspondence with PL lifetime observations, this value decreases to  $\sim 32\%$  for an  $\text{Eu}_2\text{O}_3$  concentration of 8 mol%. In parallel, the absorbance increases, what leads to the observed plateau in emission intensity. The absorbance at 394 nm is  $\sim 50\%$  for  $x = 0.5$ , and increases to  $\sim 94\%$  for  $x = 4$ . Quantum yield therefore increases from  $\sim 40\%$  to  $\sim 60\%$  for an  $\text{Eu}_2\text{O}_3$  concentration of up to 2 mol%. At higher concentration, it commences to decrease (Fig. 3b). This means that at the optimal  $\text{Eu}_2\text{O}_3$  doping concentration of  $\sim 2 \text{ mol}\%$ , about two thirds of the incoming photons are absorbed and re-emitted through  $\text{Eu}^{3+}$  photoluminescence in the red spectral range.

## Conclusions

In conclusion, heavily  $\text{Eu}_2\text{O}_3$  doped  $\text{Y}_2\text{O}_3\text{-Al}_2\text{O}_3\text{-B}_2\text{O}_3$  represents a high-gain red-emitting material for UV-to-red photoconversion with a conversion efficiency of up to 60 %. We related concentration quenching to the occurrence of -{Eu-O-Me-O-Eu}- (Me = B, Y, Al) and -{Eu-O-Eu}- entities in the first and second coordination shell, respectively, of  $\text{Eu}^{3+}$ . For a quantitative consideration, we proposed a statistical approach to estimate the number of those species as a function of europium concentration. In this way, a crossover was found for a dopant concentration of  $\sim 3 \text{ mol}\%$  of  $\text{Eu}_2\text{O}_3$  where further addition of europium directly increases the number of -{Eu-O-Eu}- in which the critical distance for concentration quenching of PL is achieved. This observation is confirmed experimentally through lifetime analyses as well as quantum efficiency

measurements. The proposed tool can now be used to predict and optimize cluster formation and concentration in rare-earth doped glasses.

## Acknowledgement

Parts of this work have been supported financially by the German Science Foundation through its priority program 1594 (grant. no. WO1220/10-1). The authors further acknowledge financial support from the Department of Education of Guangdong Province (Grant No. 2013gjh0001).

## Notes and references

<sup>1</sup>Otto Schott Institute of Materials Research, University of Jena, 07743 Jena, Germany

<sup>2</sup>State Key Laboratory of Luminescent Materials and Devices, School of Materials Science and Technology, South China University of Technology, 510641 Guangzhou, China.

<sup>3</sup>The Chinese-German Research Center for Photonic Materials and Devices at South China University of Technology, 510641 Guangzhou, China.

\*lothar.wondraczek@uni-jena.de

- G. Blasse and B. C. Grabmaier, *Luminescent materials*, Springer-Verlag, 1994.
- G. Gao, N. Da, S. Reibstein and L. Wondraczek, *Opt. Express*, 2010, **18**, A575–A583.
- G. Gao, S. Reibstein, M. Peng and L. Wondraczek, *J. Mater. Chem.*, 2011, **21**, 3156–3161.
- D. K. Williams, B. Bihari, B. M. Tissue and J. M. McHale, *J. Phys. Chem. B*, 1998, **102**, 916–920.
- J. C. Boyer, F. Vetrone, J. A. Capobianco, A. Speghini and M. Bettinelli, *J. Phys. Chem. B*, 2004, **108**, 20137–20143.
- Z. Qi, C. Shi, W. Zhang, W. Zhang and T. Hu, *Appl. Phys. Lett.*, 2002, **81**, 2857–2859.
- C.-H. Yan, L.-D. Sun, C.-S. Liao, Y.-X. Zhang, Y.-Q. Lu, S.-H. Huang and S.-Z. Lu, *Appl. Phys. Lett.*, 2003, **82**, 3511–3513.
- G. Gao and L. Wondraczek, *J. Mater. Chem. C*, 2013, **2**, 691–695.
- A. Goetzberger and W. Greube, *Appl. Phys.*, 1977, **14**, 123–139.
- H. Lin, D. Hou, L. Li, Y. Tao and H. Liang, *Dalton Trans.*, 2013, **42**, 12891–12897.
- B. Tian, B. Chen, Y. Tian, X. Li, J. Zhang, H. Zhong, L. Cheng, S. Fu, H. Zhong, Y. Wang, X. Zhang, H. Xia and R. Hua, *J. Mater. Chem. C*, 2013, **1**, 2338–2344.
- L. Wondraczek, M. Batentschuk, M. A. Schmidt, R. Borchardt, S. Scheiner, B. Seemann, P. Schweizer and C. J. Brabec, *Nat. Commun.*, 2013, **4**, 2047.
- X. Huang, S. Han, W. Huang and X. Liu, *Chem. Soc. Rev.*, 2012, **42**, 173–201.
- M. Peng and L. Wondraczek, *J. Mater. Chem.*, 2009, **19**, 627–630.
- E. Downing, L. Hesselink, J. Ralston and R. Macfarlane, *Science*, 1996, **273**, 1185–1189.
- H. L. Rutz, D. E. Day and C. F. Spencer, *J. Am. Ceram. Soc.*, 1990, **73**, 1788–1790.
- G. Gao and L. Wondraczek, *Opt. Mater. Express*, 2013, **3**, 633–644.
- D. R. S. Santos, C. N. Santos, A. S. S. de Camargo, W. F. Silva, W. Q. Santos, M. V. D. Vermelho, N. G. C. Astrath, L. C. Malacarne, M. S. Li,

- A. C. Hernandez, A. Ibanez and C. Jacinto, *J. Chem. Phys.*, 2011, **134**, 124503.
19. A. Brenier, D. Jaque and A. Majchrowski, *Opt. Mater.*, 2006, **28**, 310–323.
20. R. D. Shannon, *Acta Crystallogr. A*, 1976, **32**, 751–767.
21. O. Bouty, J. M. Delaye and S. Peuget, *Procedia Chem.*, 2012, **7**, 540–547.
22. Y. Shimizugawa, N. Umesaki, J. Qiu and K. Hirao, *J. Synchrotron Radiat.*, 1999, **6**, 624–626.
23. R. Balda, J. Fernández, J. L. Adam and M. A. Arriandiaga, *Phys. Rev. B*, 1996, **54**, 12076–12086.
24. P. Babu and C. K. Jayasankar, *Physica B Condens. Matter*, 2000, **279**, 262–281.
25. A. Ivankov, J. Seekamp and W. Bauhofer, *J. Lumin.*, 2006, **121**, 123–131.
26. H. Deters, J. F. de Lima, C. J. Magon, A. S. S. de Camargo and H. Eckert, *Phys. Chem. Chem. Phys.*, 2011, **13**, 16071–16083.
27. G. Gao and L. Wondraczek, *Opt. Mater. Express*, 2014, **4**, 476–485.
28. S. Iftekhar, B. Pahari, K. Okhotnikov, A. Jaworski, B. Stevansson, J. Grins and M. Edén, *J. Phys. Chem. C*, 2012, **116**, 18394–18406.
29. T. Murata, Y. Moriyama and K. Morinaga, *Sci. Technol. Adv. Mater.*, 2000, **1**, 139–145.
30. A. A. Reddy, S. Das, S. Ahmad, S. S. Babu, J. M. F. Ferreira and G. V. Prakash, *RSC Adv.*, 2012, **2**, 8768–8776.
31. G. Gao and L. Wondraczek, *J. Mater. Chem. C*, 2013, **1**, 1952–1958.
32. C. Xu, Y. Li, Y. Huang, Y. M. Yu and H. J. Seo, *J. Mater. Chem.*, 2012, **22**, 5419–5426.
33. B. S. Richards, *Sol. Energy Mat. Sol. C.*, 2006, **90**, 1189–1207.
34. G. Jia, M. Yang, Y. Song, H. You and H. Zhang, *Cryst. Growth Des.*, 2009, **9**, 301–307.

We employ a statistical approach to estimate the number of photoluminescence quenching species as a function of doping concentration.

