

RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

SYNOPSIS TOC

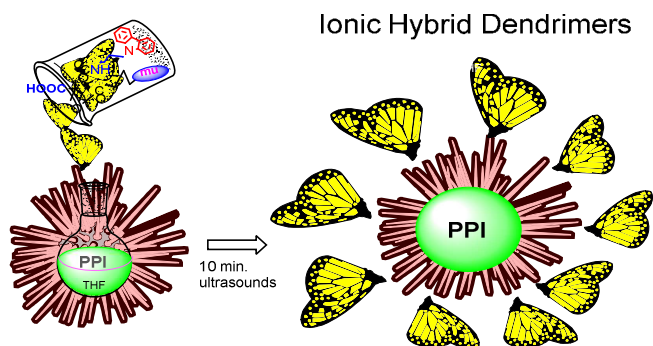

Title: Multifunctional Ionic Hybrid Poly(propyleneimine) Dendrimers surrounded by Carbazole Dendrons: Liquid Crystals, Optical and Electrochemical Properties.

Authors: Susana Castelar, Pilar Romero, José-Luis Serrano, Joaquín Barberá*, Mercedes Marcos*

Text: Hybrid ionic dendrimers prepared via ionic self-assembly by grafting of cationic PPI dendrimer with anionic bifunctional dendrons that containing electroactive carbazole groups on their periphery, display photoluminescence properties and ability to self-assemble into nematic, smectic or columnar mesophases.



Journal Name

ARTICLE

Multifunctional Ionic Hybrid Poly(propyleneimine) Dendrimers surrounded by Carbazole Dendrons: Liquid Crystals, Optical and Electrochemical Properties

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Susana Castelar^a, Pilar Romero^a, José-Luis Serrano^b, Joaquín Barberá^{a*}, Mercedes Marcos^{a*}

Two novel series of dendrimers constituted by the ionic grafting of poly(propylene imine) PPI-(NH₂)_n (n=4, 8, 16, 32, 64 primary amines on the surface) with bifunctional dendrons of two generations (G1COOH, G2COOH) derived from 2,2-bis(hydroxymethyl)propanoic acid (bis-MPA) were prepared. The dendrons contain a carboxyl group at their apex and electroactive carbazole groups and mesogenic units on their periphery. The occurrence of proton transfer from the carboxylic acid to the amine groups was confirmed by IR and NMR measurements. The liquid crystalline behavior has been investigated by means of differential scanning calorimetry (DSC), polarizing optical microscopy (POM) and X-ray diffractometry (XRD). All ionic dendrimers were liquid crystalline (nematic, smectic or columnar mesophases). The type of mesophase depends on the dendrimer generation as well as on the dendron generation. The electrochemical behavior of the ionic dendrimers was investigated by cyclic voltammetry (CV). Scanning electron microscopy (SEM) studies revealed that electrochemical deposition of the material on the conducting substrate takes place. The UV-Vis absorption and emission properties of the ionic hybrid dendrimers have been investigated. All the compounds are luminescent at room temperature and the intensity is related to the number of carbazole units present in the molecule.

Introduction

Dendrimers are monodisperse, highly branched macromolecules that have attracted significant interest in material science and biomedicine fields.¹⁻⁴ Their unique architecture originates novel properties, such as better solubility and lower viscosity than their analogous linear polymers. Moreover the high density of functional groups contained in their structure allows the introduction of a higher number of active units with specific properties.

In these materials, using a similar approach than in side chain liquid crystals polymers (SCLCP), the incorporation of promesogenic units on the periphery of the dendrimeric structures allow us to obtain liquid crystals dendrimers.⁵ The majority of these mesogenic dendrimers has been obtained using a covalent attachment of the molecules,⁶ but also the ionic attachment of molecules bearing a carboxylic group to the amine terminal groups of the poly(propylene imine) (PPI) and poly(amidoamine) (PAMAM) dendrimers has demonstrated to

be an easy and versatile strategy to produce mesomorphic materials.⁷ Using this method the incorporation of different functional units could be used in order to prepare multifunctional materials for specific applications. Thus the incorporation of photoactive molecular units, such as carbazole, into liquid crystalline polymers may offer advantages over conventional polymers.⁸ It is important to take account that carbazole is one of the most familiar electron donors and it has been widely used in the design of fluorescent and hole-transporting materials.⁹ Thus Preece et al.¹⁰ describe in 2001 the first columnar liquid crystal containing carbazole units and in 2002 Velasco et al.¹¹ describe the first carbazole-based lamellar liquid crystal system. Later other liquid crystals functionalized with carbazole units have been reported in the literature.¹² In 2012 Manickam et al. have published an interesting review concerning carbazole-based photorefractive liquid crystal materials.¹³


Recently we have described two families of supramolecular liquid crystal dendrimers based on the self-assembly of carbazole-derived dendrons as the electron-donating group and an electron accepting 1,3,5-triazine core. The photoconductivity of these materials was studied. It was concluded that all of the compounds, both dendrons and complexes, exhibited photoconductivity of the same order of magnitude.¹⁴

a) Departamento de Química Orgánica, Facultad de Ciencias-Instituto de Ciencia de Materiales de Aragón, Universidad de Zaragoza-CSIC, 50009 Zaragoza, Spain

b) Departamento de Química Orgánica, Facultad de Ciencias, Instituto de Nanociencia de Aragón, Universidad de Zaragoza, 50009 Zaragoza, Spain
E-mail: mmarcos@unizar.es

E-mail: jbarbera@unizar.es


* Electronic Supplementary Information (ESI) available: Text giving more details about the employed techniques including reaction schemes and structures, optical studies, synthesis and characterization of the materials, and DSC data, figures showing the compound structure, NMR and IR spectra, and DSC curves, and optical data. See DOI: 10.1039/x0xx00000x

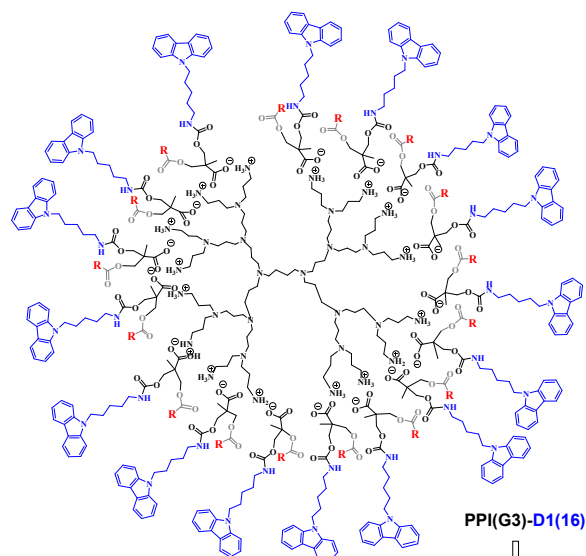

Supramolecular Ionic Hybrid Dendrimers with First Generation Dendrons

PPI(G3)-D1(16)

PPI₁₆CzX1

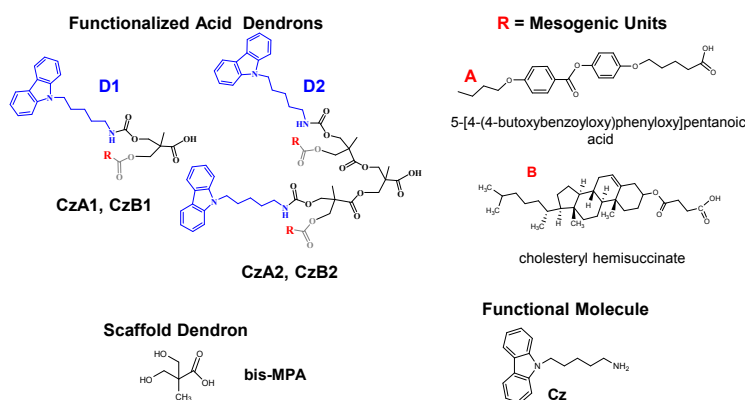

Scheme 1. Schematic representation and nomenclature of the reported dendrons (Cz_xm) and dendrimers (PPI)_nCz_xm. The hybrid dendrimer with third generation of PPI G3 and a first generation Dendron (D1) is represented.

To date, hybrid dendrimers consisting of two different dendritic polymeric segments are very scarce.^{8d,15} As a continuation of our investigations, the aim of this work is to prepare, through ionic bonding, functional ionic hybrid liquid crystal dendrimers to use the mesomorphic properties as a tool to organize these materials and to evaluate the luminescence and electrochemical properties. Two novel families of dendrimers were synthesized from poly(propylene imine) (PPI) dendrimer generations 1 to 5 (bearing 4, 8, 16, 32,

64 NH₂ terminal groups). The PPI was surrounded by carboxylic acid dendrons of two generations G1 and G2 (in future we will denote as D1 and D2 in order to avoid a mistake with the generations of PPI G=1-5) bifunctionalized with promesogenic units (family A derived from 5-[4-(4-butoxybenzoyloxy)phenoxy]pentanoic acid and family B derived from cholesteryl hemisuccinate) and carbazole groups as peripheral hole-transporting moieties and fluorescent units.

The structure of ionic hybrid dendrimers and dendrons are shown in Scheme 1.

Nomenclature. Carboxylic acid dendrons used to prepare the dendrimers are denoted as CzXm, where Cz indicates carbazole unit, m refers the generation of dendrons (D1 and D2) and X represent the promesogenic units (X= A: 5-(4-(4-butoxybenzoyloxy)phenoxy)pentanoic acid and X= B: Cholesteryl hemisuccinate). The hybrid ionic dendrimers are denoted PPI_nCzXm, where PPI represent the poly(propylene imine) dendrimer core and n refers to the number of amino groups (n = 4, 8, 16, 32, 64, that correspond at G=1-5 respectively).

EXPERIMENTAL

Synthesis

Dendritic carboxylic acids. The synthesis of the bifunctionalized dendrons CzXm was described in a previous paper^{14a} and was carried out according to the method described by Frechet et al.¹⁶ The reaction involves nucleophilic attack by the carbazole-containing amine to a cyclic carbonate derived from 2,2-bis(hydroxymethyl)propanoic acid (bis-MPA). This leads to the formation of a carbamate linkage with concomitant generation of a hydroxyl group, which can subsequently be reacted with a carboxylic acid. Thus, two different moieties can be added in immediate succession without any deprotection steps or functional group conversions. The synthetic route is shown in Scheme 1.

Ionic hybrid dendrimers. Ionic hybrid dendrimers were synthesized by a procedure previously described by us^{7c} following the method of Crooks¹⁷ (see Scheme 2).

The corresponding carbazole-containing dendritic carboxylic acid CzXm (n equiv) was dissolved in anhydrous tetrahydrofuran (THF). The solution was added to a solution of the corresponding generation (PPI-(NH₂)_n) (1 equiv) in anhydrous THF and the mixture was sonicated for 5 minutes. The solvent was then slowly evaporated at room temperature and the resulting solid was dried in vacuum to constant weight for ca. 12 h at 40 °C.


RESULTS AND DISCUSSION

Characterization of the ionic hybrid dendrimers. The formation of ionic interactions between the PPI dendrimer and the dendron acids was studied by infrared (IR) spectroscopy and by nuclear magnetic resonance (NMR) in deuterated chloroform solution.

FT-IR characterization. The main IR data for dendrimers are gathered in Table S1.

It can be seen, as an example, which the carbonyl group region of the dendron two nearly overlapped bands can be observed at 1737 and 1729 cm⁻¹, assigned to the carbonyl groups of the

carboxylic acid and ester, respectively. When the ionic pairs are formed, the signal at 1737 cm⁻¹ disappears and two bands at 1576 and 1405 cm⁻¹ corresponding, respectively, to the asymmetric and symmetric stretching modes of the carboxylate groups in the hybrid ionic dendrimer PPI₁₆CzB1 appeared, whereas the signal at 1728 cm⁻¹ corresponding to the ester remains, (Figure S1).

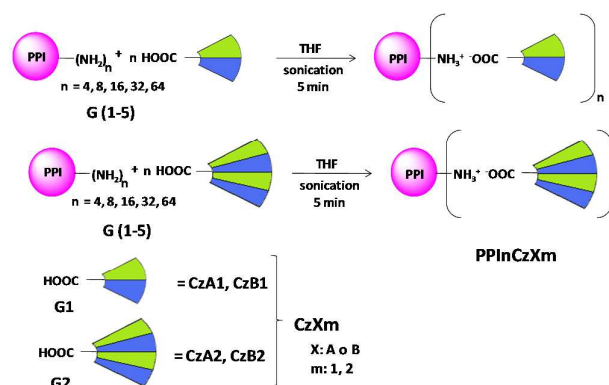

Scheme 2. Synthetic route of ionic hybrid dendrimers derived from PPI dendrimers and bis-(MPA) bifunctionalized dendrons. PPI is represented in pink. In the carboxylic acid dendrons the carbazole-containing moiety is represented in blue and the mesogenic unit in green.

Changes in the region for N–H bonds can also be observed: two bands, corresponding to the N–H bonds of the PPI dendrimer core, disappear and are replaced by a broad band between 3600–3200 cm⁻¹, corresponding to the protonated amines (NH³⁺) of PPI and the N–H bonds of the carbamate groups.

NMR Characterization. The chemical structures of the ionic dendritic polymers were analyzed by one-dimensional ¹H and ¹³C NMR and two-dimensional ¹H–¹H COSY, ¹H–¹³C HSQC and ¹H–¹³C HMBC NMR. The results obtained confirm the formation of the salts and, as representative examples, ¹H NMR data for carboxylic acids and the ionic complexes derived from PPI_nCzXm are collected in Table S2 and are shown in Figure S2. The total ¹H and ¹³C assignments of dendrons are described in our previous paper.^{14a} In Figures S2 and S3 we show ¹H NMR and ¹³C NMR spectra of CzB1 and its corresponding dendrimers of the 3rd, 4th and 5th generations were only we indicate the main signals involved in ionic interactions.

The signals corresponding to the protons of the acid groups are very broad and are barely visible in the ¹H spectrum. As a consequence, these signals cannot be taken into account to discuss the formation of the salts. The highest chemical shifts in the dendron part are related to the nuclei nearest to the focal point. Thus, the signals for the protons of the diastereotopic methylene (H_{s,s'}, see Figure S2) and the methyl group β to the carboxylic acid group (H_β) move to higher field in the carboxylate but the signal due to the proton of the carbamate group (–OCONH–) is shifted downfield. Protonation of the primary amine groups on the dendrimer surface is

confirmed by the downfield shift of the HB signal α to the terminal amino group (~ 0.3 ppm).

^{13}C NMR is more sensitive to this effect than ^1H NMR and there are two main pieces of evidence in this respect. Firstly, when the amine is protonated, the signal for the carbon α to NH_2 (CB) moves from 40.2/40.6 ppm to 38.6 ppm (data confirmed by an HSQC experiment) and the shifts of the carbon signals belonging to the dendron (Cs,s') move from 65.48 ppm and 65.78 ppm to 66.84 ppm and 67.24 ppm, respectively. Moreover, the ^{13}C signal of the carboxylic acid group (Cz) is shifted to lower field by between +1 and +4 ppm, the signal for the methylic carbon (Cu) β to the carboxyl group is shifted to lower field from 17.60 ppm to 18.77 ppm and the ^{13}C signal of the carbamate group (C6) is also deshielded (from 155.89 ppm to 156.81 ppm) (see Figure S2).

The strength of the ionic interaction in solution was assessed by diffusion NMR (DOSY). These studies were carried out on a dendron (CzB1), on PPI dendrimers and on three of zwitterionic dendrimers corresponding to generations 3, 4 and 5 of the PPI dendrimer. Once the diffusion coefficients had been obtained relative to an internal standard¹⁸ (TMS) it was observed that the ionic dendrimers behave as single molecules in solution, with only a single diffusion coefficient observed (Figure 1).

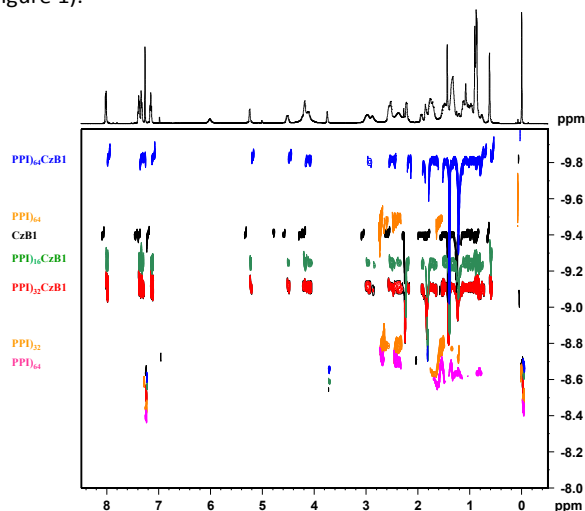


Fig. 1. ^1H DOSY NMR spectra of dendron CzB1, PPI derivatives of the 3rd, 4th and 5th generation and their related ionic dendrimers PPI₁₆CzB1, PPI₃₂CzB1, PPI₆₄CzB1 (500 MHz, CDCl_3 , 25 °C). The projection corresponds to PPI₃₂CzB1.

This finding confirms that the ionic bond is strong enough to keep the two parts of the ionic dendrimer linked in solution. In previous studies on different ionic dendrimers^{7c,19} our group found that in solution the bond strength was not sufficiently high to keep the two parts together in the ionic dendrimer. There are examples where DOSY studies have been used to estimate the extent of ion-pairing interactions in salts, mainly in transition metal complexes²⁰ and a few on dendrimers with cations of medicinal interest.²¹ The latter study confirms the interaction between ionic molecules but these did not diffuse with the same coefficient. In our case, the coefficients are an average between those of the dendron and free PPI, except for

the generation 5 complexes which have a much lower coefficient. The relative positions of the anion and the cation were studied by NOESY experiments. It can be seen from Figure S4 that the protons of the terminal branches dock closely with diastereotopic protons of the carboxylic acid dendron and with the methyl protons (cross-peaks are indicated in Figure S4). An NOE effect between functional groups and PPI was not observed.

The signals for the aromatic protons of the dendron become more shielded on increasing the PPI generation, a trend that suggests a more compact arrangement of the dendron around the dendrimer and thus a stronger bond for PPI₆₄CzB1, which would explain its different diffusion behavior.

The downfield shift of the carboxylic carbon (Cz) signal in ^{13}C CPMAS experiments performed on CzB1 and PPI₆₄CzB1 provides evidence for the formation of the carboxylate anion (Figure S5).

Thermal stability of the dendrimers. The thermal stability of the dendrimers and carboxylic dendrons was studied by thermogravimetric analysis (TGA) under a nitrogen atmosphere (see Table S3).

Thermogravimetric analysis was used to determine the temperature at which five percent of the initial mass was lost and the onset temperatures for decomposition of these materials, both of which were found to depend on the dendron or on the generation of the dendrimer. The study of the thermal stability of the dendrons^{14a} and dendrimers indicated that the materials have good stability and in all cases the 5% weight loss are observed above the clearing point.

Liquid crystalline properties. The mesomorphic behavior of the compounds was analyzed by POM, DSC and X-ray diffraction. Three cycles were carried out in DSC experiments and data were taken from the second cycle. The DSC thermograms of these dendrimers were reproducible after the second and subsequent heating-cooling cycles. In some cases, the isotropization temperatures were taken from POM observations because transition peaks were not detected in DSC curves¹⁴. The transition temperatures are listed in Table 1. The identification of the liquid crystal phase was carried out on the basis of POM observations and was confirmed by X-ray diffraction. Of the dendrons, only CzA2 exhibits mesomorphic properties,^{14a} on the other hand, all dendrimers synthesized were liquid crystalline. Dendrimers derived from dendrons CzA1 exhibit a nematic phase for generations 1 to 4 of PPI. The nematic phase was identified by optical microscopy on applying mechanical stress to the sample showing a birefringent texture and was confirmed by X-ray diffraction, however the ionic hybrid dendrimer PPI₆₄CzA1 surrounded by 64 CzA1 (D1) dendrons exhibit a rectangular columnar mesophase. Dendrimers decorated with the dendron CzA2 (D2) exhibit a nematic phase for generations 1 to 3, however a rectangular columnar phase appears for generation 4 (32 terminal groups) of PPI dendrimer and a columnar hexagonal phase is observed for PPI G=5 (64 terminal groups).

Dendrimers derived from dendrons CzBm show a smectic A mesophase for PPI generations G = 1–4 and columnar phases

for $G = 5$. The smectic A and columnar nature of the mesophases was confirmed by X-ray diffraction. Changes in the texture or DSC peaks were not observed upon cooling the samples, indicating that the mesophase freezes into a glassy

Table 1 Transition temperatures ($^{\circ}\text{C}$) and mesogenic behavior of ionic hybrid dendrimers.

Ionic hybrid dendrimer	Transition temperature ($^{\circ}\text{C}$) ^a	Ionic hybrid dendrimer	Transition temperature ($^{\circ}\text{C}$) ^a
CzA1	C 52 I	CzA2	N _g 25 N 66 I
PPI ₄ CzA1	N _g 5 N 64 I	PPI ₄ CzA2	N _g 4 N 55 I
PPI ₈ CzA1	N _g 6 N 47 I	PPI ₈ CzA2	N _g 32 N 81 I
PPI ₁₆ CzA1	N _g 8 N 72 I	PPI ₁₆ CzA2	N _g 6 N 65 I
PPI ₃₂ CzA1	N _g 29 N 69 I	PPI ₃₂ CzA2	Col _{rg} 5 Col _h 66 I
PPI ₆₄ CzA1	Col _{rg} 10 Col _r 62 I	PPI ₆₄ CzA2	Col _{hg} 0 Col _h 61 I
CzB1	C 46 I	CzB2	C 69 I
PPI ₄ CzB1	SmA _g 50 SmA 95b I	PPI ₄ CzB2	SmA _g 75 SmA 110 I
PPI ₈ CzB1	SmA _g 42 SmA 92 I	PPI ₈ CzB2	SmA _g 72 SmA 115 I
PPI ₁₆ CzB1	SmA _g -11 SmA 100	PPI ₁₆ CzB2	SmA _g 42 SmA 89 I
PPI ₃₂ CzB1	SmA _g 35 SmA 124b	PPI ₃₂ CzB2	SmA _g 33 SmA 90 I
PPI ₆₄ CzB1	Col _{rg} 37 Col _r 117 I	PPI ₆₄ CzB2	Col _{hg} 35 Col _h 92 I

^aTransition data obtained by DSC corresponding to the second heating process performed at 10 $^{\circ}\text{C}/\text{min}$. ^bOptical data, ^cC = crystalline phase, N: nematic mesophase, SmA = smectic A mesophase, Col_h = hexagonal columnar mesophase, Col_r = rectangular columnar mesophase, N_g, SmA_g, Col_{rg}, Col_{hg}: glassy phases, I = isotropic liquid.

state that retains the liquid crystal structure. This situation was confirmed by X-ray diffraction of this glassy state. The POM textures in the SmA phase and DSC scans of two ionic hybrid dendrimers (PPI₄CzB1 and PPI₃₂CzB1) are shown in Figure 2 as examples. DSC scan for ionic hybrid dendrimers PPI₁₆CzA1, PPI₁₆B1 are shown in Figure S6.

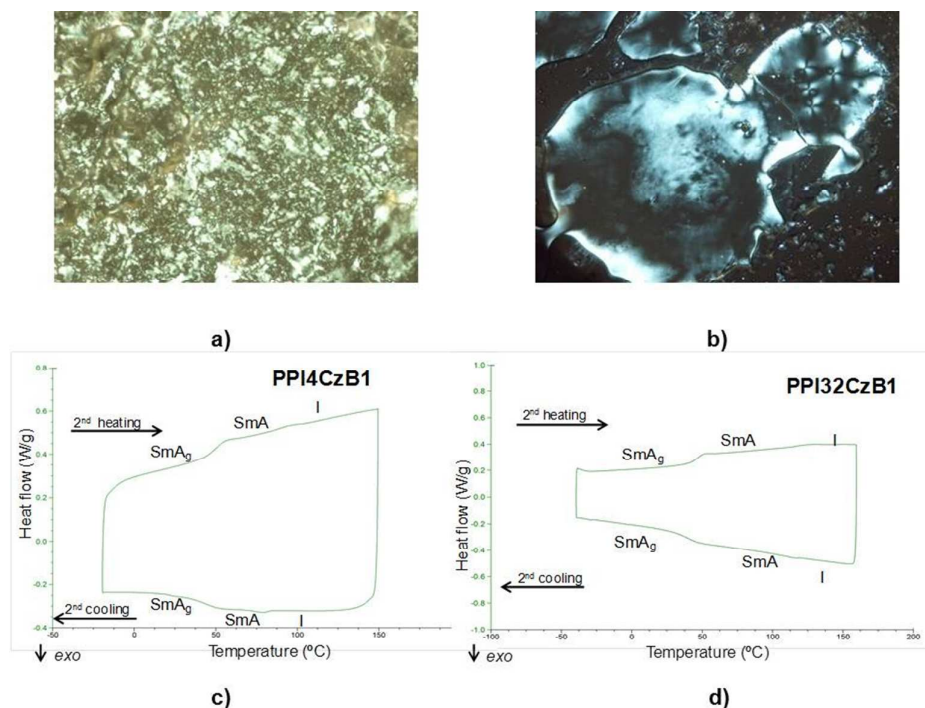


Fig. 2. a) POM texture of PPI₄CzB1 in the glassy SmA phase ($\times 10$). b) POM texture of PPI₃₂CzB1 at 94 $^{\circ}\text{C}$ in the second heating process in the SmA phase, ($\times 20$). c) DSC scan at 10 $^{\circ}\text{C}/\text{min}$ for ionic hybrid dendrimer PPI₄CzB1. d) DSC scans at 10 $^{\circ}\text{C}/\text{min}$ for ionic hybrid dendrimer PPI₃₂CzB1.

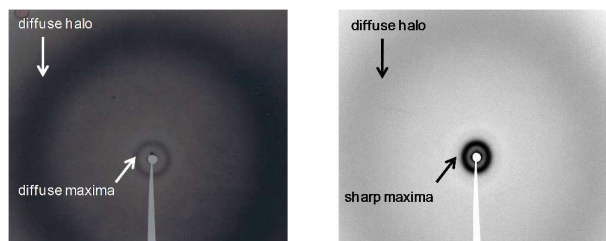


Fig. 3. Room-temperature X-ray patterns of (a) dendrimer PPI₈CzA1 in the N mesophase, (b) dendrimer PPI₁₆CzB1 in the SmA mesophase.

X-ray studies of the dendrimers

X-ray experiments were carried out on unoriented samples, in some cases at high temperatures but mostly at room temperature after thermal treatment that involved heating the sample to the isotropic liquid and then cooling it down to room temperature. Under these conditions the compounds investigated were in the liquid crystalline state, with the exception of dendrons CzA1, CzB1 and CzB2, which are not mesomorphic.

Table 2. X-ray structural parameters (Å) for the smectic mesophases.

Ionic hybrid dendrimer	Mesophase ^a	Temperature ^b (°C)	Parameters (Å)	\varnothing (Å) (Calculate)	S_d (Å ²) (Calculate)
PPI ₄ CzB1	SmA	50	$d = 42.5$	13.8	75.1
PPI ₈ CzB1	SmA	42	$d = 42.5$	19.7	76.4
PPI ₁₆ CzB1	SmA	rt	$d = 46.6$	27	71.3
PPI ₃₂ CzB1	SmA	rt	$d = 45.4$	38.7	73.5
PPI ₄ CzB2	SmA	rt	$d = 44.8$	19.1	143.8
PPI ₈ CzB2	SmA	rt	$d = 47.4$	26.4	137.2
PPI ₁₆ CzB2	SmA	rt	$d = 43.8$	39.2	151.2
PPI ₃₂ CzB2	SmA	rt	$d = 45.2$	54.7	146.9

^a SmA = smectic A mesophase, ^b rt = room temperature.

For the nematic mesophases the absence of Bragg reflections helped to confirm the absence of periodic positional order. The X-ray patterns contain a diffuse maximum in the low-angle region, which is characteristic of the local correlations along the long axis of the molecules, and a broad, diffuse halo in the high-angle region, which is typical of the conformational disorder of the aliphatic chains and is related to the local lateral interferences (Figure 3a).

The lamellar positional order inherent in the smectic mesophases produced Bragg spots that were characteristic of the layer spacing. Consequently, in addition to the high-angle broad halo related to the conformational disorder and to the

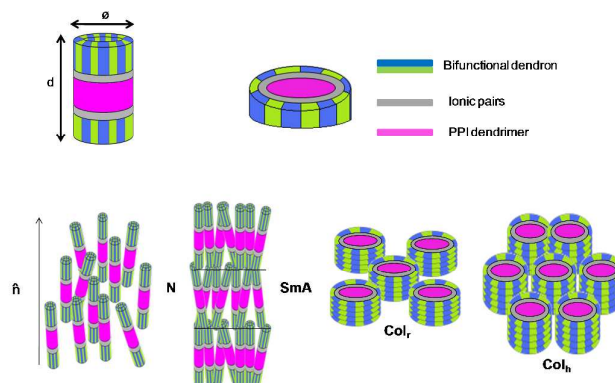


Fig. 4. Proposed arrangement of the dendrimers in the nematic, smectic A and columnar mesophases. (d : layer thickness, \varnothing : cylinder diameter; values are gathered in Table 1)

short-range correlations in the layer plane, the X-ray patterns of the smectic mesophases in this series contain one or more sharp reflections in the low-angle region, corresponding to the arrangement of the molecules in regularly spaced parallel layers. The presence of several low-angle maxima in the reciprocal spacing ratio 1:2:3: etc. is related to the successive reflection orders. However, the presence of a single maximum provided sufficient evidence to assign a smectic mesophase (Figure 3b). The deduced spacings for all of the smectic mesophases are listed in Table 2.

The data obtained are consistent with the adoption by the molecules of a cylinder-shaped conformation. In this cylinder, in a similar way to the model described for other smectic liquid crystalline dendrimers,^{6a,6c,7c} the central region is occupied by the PPI core, with the ionic pairs pointing upwards and downwards, and the dendrons are statistically distributed at both ends (Figure 4, top left). In fact, this model is valid for both the nematic and the smectic mesophases. However, in the nematic mesophase there is only orientational order and there is no positional periodicity, whereas in the smectic mesophase there is a regular arrangement in layers in addition to the orientational order (Figure 4, bottom left).

In an effort to gain an insight into the molecular arrangement and the packing in the mesophase, calculations can be carried out on the assumption that the density of the organic molecules is close to 1 g cm⁻³. Assuming that the functionalization of the terminal amino groups of PPI is complete, it is possible to estimate the diameter \varnothing in Å of the cylindrical molecules and, from this value, the cross-section S_d

in \AA^2 of each dendron considered perpendicular to the cylinder axis (see SI and Figure 4, top left).

The structural parameters, the diameter of the cylindrical molecule (\varnothing) and the cross-section of each dendron (Sd) in the smectic (SmA) mesophase are listed in Table 2. These data show that the cylinder height (d, layer spacing) does not change appreciably on varying the generation of the dendrimer or of the dendron. This trend is in reasonable agreement with the results found for other smectic liquid crystalline dendrimers and is due to the predominant spreading of the dendritic branches of PPI in the plane perpendicular to the cylinder axis, a situation that arises in order to accommodate all the dendrons. Furthermore, it is observed that the surface required by the second-generation dendrons (145\AA^2 on average) is approximately twice the surface required by the first-generation dendrons (74\AA^2 on average), which is consistent with the proposed cylindrical arrangement. Moreover, as mentioned below, the occurrence of columnar mesomorphism for a lower generation of PPI in the case of the second-generation dendron can be accounted for by its higher space requirements, which force the dendrimers to change their conformation from cylindrical to disc-like for a lower generation.

Table 3. X-ray structural parameters (\AA) for the columnar mesophases

Ionic hybrid dendrimer	Mesophase	T (°C)	Parameters (\AA)	d_{obs} (\AA)	d_{calc} (\AA)	h_d^b (\AA)	h_k
PPI ₆₄ CzA1	Col _r	rt	a = 69.3	42.3	42.3	51.3	11
			b = 53.4	26.7	26.7		02
PPI ₆₄ CzB1	Col _r	37 ^a	a = 73	45.4	45.4	49.8	11
			b = 58	28.8	29		02
PPI ₃₂ CzA2	Col _r	rt	a = 62.8	39.4	38.9	59.2	11
			b = 50.6	25.3	25.1		02
PPI ₆₄ CzA2	Col _h	rt	a = 55.6	48.1	48.1	70.3	10
				27.9	27.8		11
PPI ₆₄ CzB2	Col _h	rt	a = 55.9	48.8	48.4	88.1	10
				27.6	27.9		11

^a Data obtained at 37 °C in the heating process. b Disc thickness ($h_d = 10 \times M / (6.023 \times a \times (b/2))$) for the Col_r phase and $hd = 10 \times M / (6.023 \times (\sqrt{3}/2) \times a^2)$ for the Col_h phase). rt: room temperature. Col_r: rectangular columnar mesophase, Col_h: hexagonal columnar mesophase.

The evolution from smectic to columnar mesomorphism is related to this conformational change. Indeed, in the case of dendron CzB1 it can be observed that the molecule diameter \varnothing increases with the PPI generation (Table 2) until a situation is reached where the molecule adopts the shape of a flattened cylinder, the diameter of which is almost equal to its height (PPI₃₂CzB1). For a higher PPI generation a situation is reached in which the cylinder cross-section does not have enough space to accommodate the increasingly large number of dendrons. At this point, a dramatic conformational change takes place and the dendrons arrange themselves around the PPI core because the steric hindrance encountered in the

cylindrical arrangement is relieved if the dendrons shift to a radial orientation, thus yielding a disc shape (Figure 4, top right).

When this disc-like arrangement is achieved, the molecules stack in columns and these columns pack in a two-dimensional lattice with rectangular symmetry for PPI₆₄CzA1, PPI₆₄CzB1 and PPI₃₂CzA2 (Figure 4, bottom right). Columnar mesophases yield X-ray diffraction patterns that contain a set of sharp maxima in the low-angle region, which are characteristic of the two-dimensional packing of columns, and a broad, diffuse halo at high angles, which is typical of the conformational disorder of the aliphatic chains and is consistent with the absence of a regular stacking distance along the column axis. The measured spacing and the deduced structural parameters are given in Table 3. The rectangular symmetry of the columnar packing for these three compounds is deduced from the presence of two low-angle sharp maxima that can be assigned, respectively, to the (1 1) and (0 2) reflections of the two-dimensional rectangular lattice, from which the lattice constants a and b are obtained.

When the highest PPI generation is ionically bonded to second-generation dendrons (compounds PPI₆₄CzA2 and PPI₆₄CzB2), the mutual balance between the distinct regions of the molecule produces a different spatial arrangement and a hexagonal symmetry is generated (Figure 4, bottom right). The hexagonal symmetry is deduced from the presence of two low-angle sharp maxima in the reciprocal spacing ratio 1:√3, which are assigned, respectively, to the (1 0) and (1 1) reflections of the two-dimensional hexagonal lattice, from which the lattice constant a is obtained. As for the rectangular columnar mesophases in this series, only a broad, diffuse halo is observed in the high-angle region. As for the smectic mesophases, simple calculations can be carried out for the columnar mesophases in order to gain an insight into the packing in the liquid crystal phase. These calculations enable values for hd to be estimated (Table 3; see SI). This parameter is the mean disc thickness or, expressed otherwise, the height of column required to accommodate one molecule. Comparison of the hd values with the lattice constants gathered in Table 3 indicates that these molecules in the columnar mesophases have a considerable thickness compared to their cross-section and, therefore, their shape is more appropriately described as cylindrical than disc-like. Another significant conclusion drawn from the hd values gathered in Table 3 is related to their evolution upon changing the PPI generation. On considering dendron CzA2, the only one that is present in the two hybrid dendrimers collected in Table 3 (PPI₃₂CzA2 and PPI₆₄CzA2), the difference in hd on increasing the PPI generation from 4 to 5 is 11 Å. This is consistent with the data reported in the literature for similar situations and is accounted for by a preferential elongation of the PPI branches in the direction of the column axis.²²

Optical properties

The UV–vis absorption and emission spectra of the hybrid dendrimers were recorded in dichloromethane solution

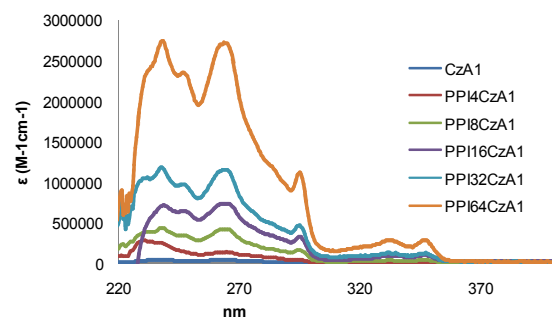


Fig. 5. Normalized UV-vis absorption spectra in CH_2Cl_2 solution of dendron CzA1 and the dendrimers $\text{PPI}_n\text{CzA1}$.

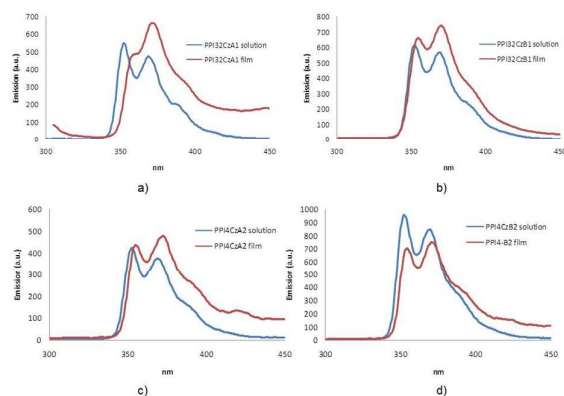


Fig. 6. Emission spectra in CH_2Cl_2 solution and in the mesophase film of a) $\text{PPI}_{32}\text{CzA1}$, b) $\text{PPI}_{32}\text{CzB1}$, c) $\text{PPI}_4\text{CzA2}$, d) $\text{PPI}_4\text{CzB2}$

(10^{-5} M for absorption and 10^{-7} M for emission) and also on films cast at room temperature. The data are summarized in Tables S4 and S5. Only data for hybrid dendrimers of $\text{PPI}_n\text{G} = 1$ and dendrons D1 (CzA1, CzB1) are discussed because the other generations exhibit a similar behavior.

In the UV region all of the hybrid dendrimers present absorption bands at 265 nm, 295 nm and 332 nm, which are assigned to carbazole-centered transitions, $\pi-\pi^*$ transitions and $n-\pi^*$ transitions, respectively. The emission spectra (excitation at 295 nm) all exhibit two bands at 352 nm and 369 nm along with a shoulder at 388 nm.

The absorption spectra of dendron CzA1 and the corresponding ionic hybrid dendrimers are shown in Figure 5. As can be observed, the molar absorbance of the peaks increases in a linear manner with the number of carbazole rings in the dendrimer (related to the generation of the dendrimer PPI_n , series A).

Comparison of the molar absorbance value for each dendrimer at 265 nm with the value obtained for the dendron confirms the situation outlined above. The relevant data are collected in Tables S6 and S7. On the other hand, it was observed that dendrimers $\text{PPI}_n\text{CzB1}$ show a slight deviation from linearity in this behavior. Quantum yields for the $\text{PPI}_n\text{CzB1}$ family were measured with quinine sulfate monohydrate as a standard ($\phi = 0.546$ in 1N H_2SO_4). The values lie in the range 0.09–0.10 and the lowest quantum yield was observed for the first

generation hybrid ionic dendrimer ($n = 4$) $\text{PPI}_4\text{B1}$ (data are gathered in Table S8).

The emission of the dendrimers was studied and it was found that the peak maxima are similar in both series derived from dendrons A and B [around 352, 369, 388 (sh) in solution and 355, 372, 389 (sh) in film].

The bands in the emission spectra in mesophase appear broader than the corresponding emission bands in the in solution (Figure 6). This difference is more noticeable for dendrimers of family A, probably due to the greater ability of the dendrimers of series PPI_nCzAm to engage in $\pi-\pi$ interactions between the aromatic rings of the promesogenic unit and the carbazole groups when compared to those of series B. This effect gives rise to a more marked red-shift for the compounds derived from CzAm dendrons. The absorption spectra of dendrons and ionic hybrid dendrimers $\text{PPI}_n\text{CzA1}$ and $\text{PPI}_n\text{CzB1}$ are shown in supporting information (Figure S7)

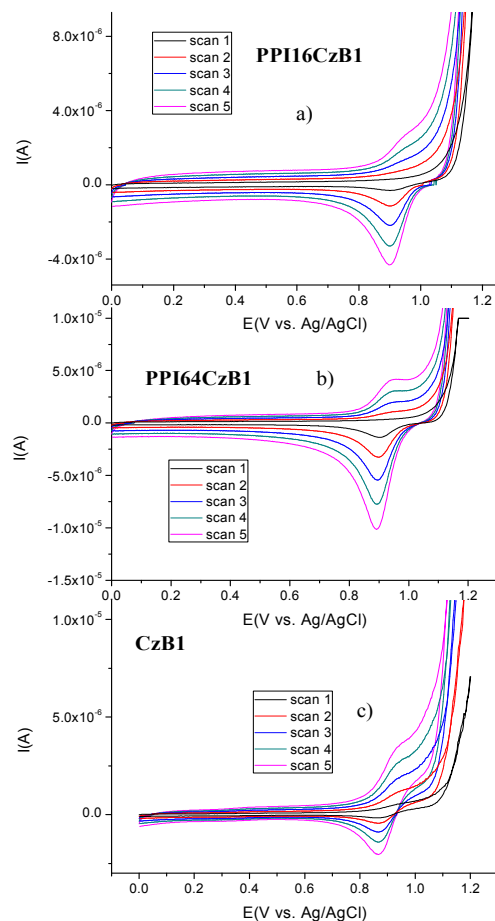


Fig. 7. Cyclic voltammograms of the first five cycles of: a) $\text{PPI}_{16}\text{CzB1}$, b) $\text{PPI}_{64}\text{CzB1}$, c) CzB1.

Electrochemical properties

The electrochemical behavior of the ionic hybrid dendrimers was investigated by cyclic voltammetry (CV) and the results are summarized in Table S9.

The potential was cycled between 0 and 2 V at a scan rate of 100 mV⁻¹ against an Ag/AgCl reference electrode with a platinum auxiliary electrode and a graphite working electrode. In the first cycle of the CV scan the anodic peaks of the dendrimer are more intense than the cathodic peaks. This marked asymmetry in the redox couple indicates that these species undergo irreversible oxidation.

The dendrimers were studied in five cycles and representative CV curves are shown in Figures 7 and S8.

Cyclic voltammetry traces obtained using ITO as the working electrode and with the potential cycled between 0 and 2 V were also studied in order to assess whether electropolymerization of the samples occurred (Figure 7).

It can be observed that the *intensity* of the oxidation peak increases in successive cycles but the intensity of the reduction peak increases to a lesser extent. In addition, the formation of an electrodeposited film of the ionic hybrid dendrimers takes place on the ITO working electrode. This effect was not observed with the dendrons

Conclusions

A new polymeric liquid crystal architecture (ionic hybrid liquid crystalline dendrimers) has been designed and synthesized by complexation between a dendrimer template derived from PPI-(NH₂)_n and an electron-donating carbazole dendron shell. The systems are constructed by the formation of ion pairs between the carboxylic acid group of the dendron and the terminal amine groups of the dendrimer.

All of the dendrimers are mesogenic and the mesophase type depends on the generation of dendrimer and the dendron type. Dendrimers derived from CzAm dendrons show nematic and columnar mesomorphism, whereas dendrimers derived from CzBm dendrons exhibit smectic A and columnar mesophases.

All of the systems are luminescent at room temperature in solution and in films, and the intensity of the emission and absorption depends on the number of carbazole units in the dendrimer.

All compounds have electrochemical properties due to presence of carbazole rings, but it was observed that the oxidation behaviour does not depend on the dendrimer generation.

Acknowledgements

This work was supported by MINECO Spain, under Project CTQ2012-35692 and FEDER funding, EU, and by the Gobierno de Aragón (Research Group E04). S.C. thanks the MICINN (Spain) for an FPI grant. The authors also acknowledge the Microscopy Service of the Universidad de Zaragoza, and Nuclear Magnetic Resonance, Mass Spectrometry, Elemental

Analysis and Thermal Analysis Services of CEQMA, Universidad de Zaragoza-CSIC (Spain)

Notes and references

- (1) a) J. M. J. Fréchet, D. A. Tomalia, *Dendrimers and Other Dendritic Polymers*, Wiley, Hoboken, 2001; b) D. A. Tomalia, J. B. Christensen, U. Boas, *Dendrimers, Dendrons, and Dendritic Polymers: Discovery, Applications, and the Future*, Cambridge University Press, New York, NY, 2012.
- (2) a) G. R. Newkome, C. N. Moorefield, F. Vögtle, *Dendrimers and Dendrons: Concepts, Syntheses, Applications*, Wiley-VCH, Weinheim, 2001. b) S. El Kazzouli, S. Mignani, M. Bousminaab, J.-P. Majoral, *New J. Chem.*, 2012, **36**, 227–240
- (3) F. Vogtle, G. Richardt, N. Werner, *Dendrimer Chemistry*, Wiley-VCH, Weinheim, 2009.
- (4) D. Astruc, E. Boisselier, C. Ornelas, *Chem. Rev.* 2010, **110**, 1857–1959.
- (5) S. Hernández-Aínsa, M. Marcos, J. L. Serrano, *Dendrimeric and Hyperbranched Liquid Crystal Structures*, Handbook of Liquid Crystals: 8 Volume Set, Second Edition.; J. W. Goodby, P. J. Collings, T. Kato, C. Tschierske, H., Gleeson, P. Raynes, Eds.; Wiley-VCH Verlag GmbH & Co. KGaA: 2014; Vol. 8, p 259-300.
- (6) (a) M. W. P. L. Baars, S. H. M. Söntjens, H. M. Fischer, H. W. I Peerlings,; E. W. Meijer, *Chem. Eur. J.* 1998, **4**, 2456-2466. (b) J. Barberá, M. Marcos, J. L. Serrano, *Chem. Eur. J.* 1999, **5**, 1834-1840. (c) S. A. Ponomarenko, N. I. Boiko, V. P. Shibaev, *Polym. Sci., Ser. C* 2001, **43**, 1-45. (d) B. Donnio, D. Guillon, *Adv. Polym. Sci.* 2006, **201**, 45-155. (e) J. L. Serrano, M. Marcos, R. Martín, M. González, J. Barberá, *Chem. Mater.* 2003, **15**, 3866-3872. (f) M. Marcos, R. Martín-Rapún, A. Omenat, J. L. Serrano, *Chem. Soc. Rev.* 2007, **36**, 1889-1901. (g) B. M. Rosen, C. J. Wilson, D. A. Wilson, M. Peterca, M. R. Imam, V. Percec, *Chem. Rev.* 2009, **109**, 6275-6540. (h) C. Tschierske, *Angew. Chem. Int. Ed.* 2013, **52**, 8828-8878.
- (7) (a) K. V. Axenov, S. Laschat, *Materials*, 2011, **4**, 206-259. (b) A. G. Cook, U. Baumeister, C. Tschierske, *J. Mater. Chem.* 2005, **15**, 1708-1721. (c) R. Martín-Rapún, M. Marcos, A. Omenat, J. Barberá, P. Romero, J. L. Serrano, *J. Am. Chem. Soc.* 2005, **127**, 7397-7403. (d) A. Rapakousiou, Y. Wang, F. Nzulu, R. Djeda, N. Pinaud, J. Ruiz, D. Astruc, *Organometallics* 2013, **32**, 6079–6090.
- (8) (a) M. Belloni, B. M. Kariuki, M. Manickam, J. Wilkie, J. A. Preece, *Cryst. Growth Des.* 2005, **5**, 1443-1450. (b) J. V. Grazulevicius, P. Stroehriegl, J. Pielichowski, K. Pielichowski, *Prog. Polym. Sci.* 2003, **28**, 1297-1353. (c) V. Percec, M. Glodde, T. K. Bera, Y. Miura, I. Shiyonovskaya, K. D. Singer, V. S. K. Balagurusamy, P. A. Heiney, I. Schnell, A. Rapp, H. W. Spiess, S. D. Hudson, H. Duan, *Nature* 2002, **417**, 384-387. (d) C. Kaewtong, G. Jiang, M. J. Felipe, B. Pulpoka, R. Advincula, *ACS Nano*, 2008, **2**, 1533-1542. (e) H.-J. Son, W.-S. Han, K. H. Lee, H. J. Jung, C. Lee, J. Ko, S. O. Kang, *Chem. Mater.* 2006, **18**, 5811-5813.
- (9) a) Y. Zhang, Y. Cui, P.N. Prasad, *Phys. Rev. B* 1992, **46**, 9900-9902. b) K. Albrecht, Y. Kasai, A. Kimoto, K. Yamamoto, *Macromolecules* 2008, **41**, 3793-3800 b) S. Fukuma, K. Irie, T. Ikegami, S. Masuo, S. Machida, N. Tanaka, A. Itaya, *Journal of*

Photochemistry and Photobiology A: Chemistry 2007, **189**, 55–64. c) H. Li, R. Termine, N. Godbert, L. Angiolini, L. Giorgini, A. Golemme, *Org. Electron.*, 2011, **12**, 1184–1191; (d) J. Li, A. C. Grimsdale, *Chem. Soc. Rev.*, 2010, **39**, 2399–2410; e) W. Jiang, L. Duan, J. Qiao, G. Dong, D. Zhang, Li. Wang, Y. Qiu, J. *Mater. Chem.*, 2011, **21**, 4918–4926, f) S. Köber, M. Salvador K. Meerholz, *Adv. Mater.* 2011, **23**, 4725–4763. (g) D. Sun, Q. Fu, Ren, W. Li, H. Li, D. Mab. S. Yan, *J. Mater. Chem. C*, 2013, **1**, 5344–5350 (h) D. Sun, Q. Fu, Z. Ren, H. Li, a D. Mab, S. Yan, *Polym. Chem.*, 2014, **5**, 220–226.

(10) M. Manickam, M. Belloni, S. Kumar, S. K. Varshney, D. S. Shankar Rao, P. R. Ashton, J. A. Preece, N. Spencer, *J. Mater. Chem.* 2001, **11**, 2790–2800.

(11) E. Perea, F. López-Calahorra, D. Velasco, *Liq. Cryst.* 2002, **29**, 421–428.

(12) (a) W. Bao, M. Reddy Billa, K. Kassireddy, M. Haro, M. J. Kelly, S. P. Kitney, M. S. Al Kalifah, P. Wei, D. Dong, M. O'Neill, S. M. Kelly, *Liq. Cryst.* 2010, **37**, 1289–1303. (b) M. Manickam, P. Iqbal, M. Belloni, S. Kumar, J. A. Preece, *Isr. J. Chem.* 2012, **52**, 917–934.

(13) M. Manickam, P. Iqbal, M. Belloni, S. Kumar, J. A. Preece, *Isr. J. Chem.* 2012, **52**, 917–934 and references therein.

(14) (a) S. Castelar, J. Barberá, M. Marcos, P. Romero, J-L. Serrano, A. Golemme, R. Termine, *J. Mater. Chem. C* 2013, **1**, 7321–7332. (b) I. Gracia, B. Feringán, J. L. Serrano, R. Termine, A. Golemme, A. Omenat, J. Barberá, *Chem. Eur. J.* 2015, **21**, 1359–1369. (c) J. Wolska, J. Mieczkowski, D. Pocięcha, S. Buathong, B. Donnio, D. Guillon, E. Gorecka, *Macromolecules* 2009, **42**, 6375–6384

(15) (a) J. Guerra, A. C. Rodrigo, S. Merino, J. Tejada, J. C. García-Martínez, P. Sánchez-Verdú, V. Ceña, J. Rodríguez-López, *Macromolecules* 2013, **46**, 7316–7324. (b) Y. Liu, Y. Fan, X.-Y. Liu, S.-Z. Jiang, Y. Yuan, Y. Chen, F. Cheng, S.-C. Jiang, *Soft Matter* 2012, **8**, 8361–8369. (c) V. Perccec, J. G. Rudick, M. Peterca, M. E. Yurchenko, J. Smidrkal, P. A. Heiney, *Chem. Eur. J.* 2008, **14**, 3355–3362.

(16) A. P. Goodwin, S. S. Lam, J. M. J. Fréchet, *J. Am. Chem. Soc.* 2007, **129**, 6994–6995.

(17) V. Chechik, M. Q. Zhao, R. M. Crooks, *J. Am. Chem. Soc.* 1999, **121**, 4910–4911.

(18) E. J. Cabrita, S. Berger, *Magn. Reson. Chem.* 2001, **39**, S142–S148.

(19) M. Marcos, R. Alcalá, J. Barberá, P. Romero, C. Sánchez, J. L. Serrano, *Chem. Mater.* 2008, **20**, 5209–5217.

(20) (a) G. Bellachioni, G. Ciancaleoni, C. Zuccaccia, D. Zuccaccia, A. Macchioni, *Coord. Chem. Rev.* 2008, **252**, 2224–2238. (b) I. Fernandez, E. Martinez-Viviente, P. S. Pregosin, *Inorg. Chem.* 2005, **44**, 5509–5513. (c) P. S. Pregosin, *Prog. Nucl. Magn. Reson. Spectrosc.* 2006, **49**, 261–288.

(21) (a) E. Boisselier, C. Ornelas, I. Pianet, J. R. Aranzaes, D. Astruc, *Chem. Eur. J.* 2008, **14**, 5577–5587. (b) C. Ornelas, E. Boisselier, V. Martinez, I. Pianet, J. R. Aranzaes, D. Astruc, *Chem. Commun.* 2007, 5093–5095.

(22) J. M. Rueff, J. Barberá, B. Donnio, D. Guillon, M. Marcos, J. L. Serrano, *Macromolecules* 2003, **36**, 8368–8375.