


Cite this: *Energy Adv.*, 2024,
3, 1073

Ag/Pd bimetallic nanoparticle-loaded Zr-MOF: an efficacious visible-light-responsive photocatalyst for H₂O₂ and H₂ production†

Srabani Dash, Suraj Prakash Tripathy, Satyabrata Subudhi,  Lopamudra Acharya, Asheli Ray, Pragyandeepti Behera and Kulamani Parida *

Photocatalytic production of H₂O₂ and H₂ holds promise for conquering the impending energy crisis. In order to accomplish this goal, the photocatalysts must be robust and effective enough to harvest photons from a wide solar spectrum as well as having a high rate of exciton antirecombination. Low visible light absorption and fast recombination of exciton pairs are two major setbacks encountered in pristine MOF-based photocatalysts. Herein, the MOF UiO-66-NH₂ modified with noble bimetallic nanoparticles (Ag/Pd) was synthesized *via* a facile adsorption–reduction technique and utilized for effective photocatalytic H₂O₂ and H₂ production. The composite (1:2) Ag/Pd@UiO-66-NH₂ displayed a H₂O₂ production rate of 39.4 μmol h⁻¹ in an O₂-saturated environment in the presence of IPA and water under visible light illumination, which is almost four-fold more than that of the pristine UiO-66-NH₂ MOF and twofold greater than those of the monometallic counterparts (Ag@MOF or Pd@MOF). Moreover, the photocatalytic H₂ evolution of the prepared materials was studied and a similar trend was observed in which the composite (1:2) Ag/Pd@UiO-66-NH₂ showed the highest H₂ evolution capacity of 448.2 μmol h⁻¹. The enhanced photocatalytic performance of the Ag/Pd@MOF composite can be attributed to its ability to suppress exciton recombination, superior photon reception, and fast charge transfer. Mechanistically the transfer of photogenerated electrons from the UiO-66-NH₂ surface to the bimetallic component was promoted through the LSPR effect of Ag and this is further enhanced by the Pd support. The electron-trapping capacity of the bimetallic nanoparticle (NP)-based co-catalyst enhances the overall reaction mechanism by giving highly surface active sites on the surface for the photocatalytic production of H₂O₂ and H₂ as a sustainable means of green energy production.

Received 4th December 2023,
Accepted 30th March 2024

DOI: 10.1039/d3ya00597f

rsc.li/energy-advances

Centre for Nano Science and Nanotechnology, Siksha 'O' Anusadhan (Deemed to be University), Bhubaneswar, Odisha, 751030, India.

E-mail: paridakulamani@yahoo.com, kulamaniparida@soa.ac.in;

Fax: +91-674-2350642; Tel: +91-674-2351777

† Electronic supplementary information (ESI) available: 1. Experimental techniques (1.1. Characterization techniques, 1.2. FTO preparation, and 1.3. Scavenger test procedure); Fig. S1: BET surface area and BJH pore size distribution of (1:2) Ag/Pd@UiO-66-NH₂; Fig. S2: XPS survey spectra of UiO-66-NH₂ and (1:2) Ag/Pd@UiO-66-NH₂; Fig. S3: PL plot for UiO-66-NH₂ and (1:1, 1:2, 2:1) Ag/Pd@UiO-66-NH₂; Fig. S4: TRPL plot of (1:2) Ag/Pd@UiO-66-NH₂; Fig. S5: LSV plot of the prepared photocatalysts; Fig. S6: Post photo-catalytic PXRD analysis; Table S1: TRPL data of UiO-66-NH₂ and (1:2) Ag/Pd@UiO-66-NH₂; Table S2: apparent conversion efficiency (ACE) expression and calculation for photocatalytic hydrogen evolution by the prepared photocatalysts; Table S3: comparison of photocatalytic H₂O₂ production by various photocatalysts; Table S4: comparison of photocatalytic H₂ evolution by various photocatalysts. See DOI: <https://doi.org/10.1039/d3ya00597f>

1. Introduction

Hydrogen peroxide (H₂O₂) is considered as a green and eco-friendly oxidant, which can be treated as an active oxidant, producing water as by-product, with potential for use in extensive applications, such as pollutant degradation, waste water treatment, chemical industry, sterilization, and other environmental applications. Recently, H₂O₂ has also attracted a lot of attention as a promising energy carrier for fuel cells because it is water-soluble and can be used to generate electricity in a single-compartment cell.^{1,2} Mainly, the commercial generation of H₂O₂ follows the anthraquinone process, which includes two steps: the conversion of 2-alkyl-anthraquinone to alkyl-anthraquinone followed by high-energy oxidation and hydrogenation processes using noble-metal-based catalysts in organic solvents. As the anthraquinone process involves multiple steps and is an energy-consuming method, it is applicable only for large-scale production, and is thus considered as an environmentally unfriendly approach. To overcome this, there



has been growing research interest in the production of H_2O_2 through photocatalysis. This process mainly involves water, oxygen, semiconductors, and sunlight, and is therefore considered a green pathway. However, typically, the photocatalytic production of H_2O_2 gives low yields owing to the photocatalysts' poor visible light absorption, rapid recombination of excitons, and limited surface active sites.^{3–6}

Additionally, the photon-assisted hydrogen evolution reaction *via* water splitting has been carried out to estimate the photocatalytic characteristics of semiconducting materials. The generation of H_2 from the photocatalytic water splitting reaction has become an emerging research topic since the discovery by Fujishima and Honda's hydrogen production from H_2O using a TiO_2 semiconductor under light irradiation, with the aim of reducing the world's reliance on fossil fuels for energy.^{7–10} Moreover, the construction of a cost-effective, sustainable, and environmentally friendly photocatalytic semiconductor that is capable of performing this reaction has received much interest from the scientific community and remains a grand challenge.¹¹ Amongst the various semiconducting materials, MOFs are receiving a lot of attention owing to their exceptional characteristics, including ultra-high surface area, tuneable porosity, easy fabrication, flexible functionality, and large numbers of surface active sites. MOFs are 3D porous coordination polymers containing metal nodes/clusters that are connected with the organic linkers through coordination bonds.^{12,13} They are promising for use as photocatalysts owing to their superior light-harvesting capacity, band structure tuneability, and populous active sites. Moreover, these exceptional features boost the potential for MOFs to be used as an efficient material for several other applications, such as chemical sensing, wastewater treatment, drug delivery, and organic pollutant degradation. From the perspective of band structure, the metal centre's vacant outside orbitals contribute mostly to the valence band (VB), whereas the outer orbitals of the organic linkers contribute primarily to the conduction band (CB) of the MOF.^{14,15} Ligand to metal/cluster charge transfer, also known as LCCT or LMCT, is the process through which the linker efficiently captures sunlight and transmits energy to the metal centre. Additionally, MOFs demonstrate the two essential conditions for a water redox reaction of a proper band gap accompanied by a tolerable band edge potential and they also exhibit long-term stability against photocorrosion in aqueous solution. Among the largest family of MOFs, Zr-based MOFs such as the UiO-66 series are considered as highly stable and active materials towards various photocatalytic applications. Remarkably, the physicochemical characteristics of (Zr) UiO-66 allow them to be functionalized using substituted terephthalate linkers, such as $-\text{NH}_2$, $-\text{Br}$, and $-\text{NO}_2$.^{16–18} Thanks to these unique properties, the (Zr) UiO-66 series MOFs (UiO-66- NH_2) can be used to photocatalyze the H_2 and H_2O_2 production reactions. However, the pristine UiO-66- NH_2 MOF suffers from rapid photogenerated exciton recombination, which prevents it from becoming an efficient photocatalyst. Hence researchers have followed various strategies to improve the exciton lifetime as well as light responsiveness of the pristine UiO-66- NH_2

MOFs. Typically, these strategies involve forming a heterojunction with suitable photocatalysts, post-synthetic modification of the framework, hetero metal atom doping, and metallic nanoparticle-based co-catalyst addition. Amidst several approaches, the addition of suitable metal nanoparticles as a co-catalyst significantly improves the photocatalytic characteristics of pristine Zr-MOFs. In recent years, bimetallic nanoparticles have captured massive attention in various research fields, including sensing, plasmonics, electrocatalysis, photocatalysis, and specifically heterogeneous catalysis.^{19–22} As a new class of materials, bimetallic NPs are made up of two separate metal components. Typically, they display an amalgam of the qualities of the two component metals, thus making them superior to the individual metal components. Additionally, the physicochemical properties of bimetallic NPs can be improved through synergistic effects, such as lattice strain, electron effect, ensemble effect, and bifunctional effect. Particular attention has been focused on bimetallic cocatalysts using noble metals like Au–Ag, Ag–Pd or Au–Pd because bimetallic materials created using plasmonic materials can be useful as both charge collectors and light absorbers, thus simultaneously improving the photocatalytic performance. Hence, pristine MOFs with low photocatalytic yields demonstrate improved performance upon the addition of noble bimetallic NPs.^{23–26}

Incorporation of metal nanoparticles into MOF frameworks has received massive attention in both catalysis and photocatalysis. Typically, zirconium(IV)-based MOF UiO-66- NH_2 has drawn a lot of interest recently because of its distinctive qualities, including light harvesting, high thermal and chemical stability, variable pore sizes, large specific surface area, and the potential for functionalization.^{27,28} Amongst various noble metals, Ag nanoparticles are of interest due to the LSPR effect. Through coordination or electrostatic contact with the $-\text{NH}_2$ groups in the MOF, Ag and Pd can be immobilised on the UiO-66- NH_2 surface *via* adsorption–reduction method. The benefits of incorporating metallic Ag and Pd include an increase in light-harvesting capacity as well as the ability to control the Schottky barrier height by varying the Ag: Pd molar ratio. In this work, Ag/Pd bimetallic NP-loaded MOF nanocomposites are studied for photocatalytic H_2O_2 and H_2 production, giving significantly superior yield to that of the pristine MOF (UiO-66- NH_2).^{23,29}

2. Materials and methods

2.1. Chemicals used

Zirconium chloride (ZrCl_4), sodium tetrachloropalladate (Na_2PdCl_4), 2-amino-1,4-benzene dicarboxylic acid (BDC- NH_2), silver nitrate (AgNO_3), sodium borohydride (NaBH_4), and Nafion-117 were purchased from Sigma-Aldrich. Sodium sulphate (Na_2SO_4), *N,N*-dimethyl formamide (DMF), potassium bromide (KBr), methanol (MeOH), and isopropanol (IPA) were acquired from Merck and used without any additional



refinement. For all reactions carried out in this study deionized water was used.


2.1.1. Fabrication of UiO-66-NH₂. The fabrication of UiO-66-NH₂ was carried out according to a previously reported facile solvothermal approach.^{18,30} The synthesis process includes the separate stirring of 2-aminoterephthalic acid (0.38 g, 2 mmol) and zirconium chloride (0.47 g, 2 mmol) for 60 min in DMF as the solvent (40 mL each). The two prepared solutions were then added together and the mixture was again subjected to stirring for 60 minutes. Thereafter, the resultant solution was subjected to solvothermal treatment in a Teflon-lined autoclave (24 h/120 °C). The autoclave was subjected to gradual cooling at room temperature and then solvent exchange was done using methanol to remove the unreacted metal salt/organic parts, followed by drying in an oven (24 h/70 °C). Finally, the prepared yellow-coloured material was ground and termed as UiO-66-NH₂.

2.1.2. Fabrication of Ag@UiO-66-NH₂, Pd@UiO-66-NH₂, and Ag/Pd@UiO-66-NH₂. By following the adsorption-reduction procedure, bimetallic (Ag and Pd) nanoparticle-decorated UiO-66-NH₂ was fabricated.^{29,31} In the typical process, 0.3 g of pristine UiO-66-NH₂ was introduced to 50 mL of water/methanol solution (1:1, v/v) followed by continuous stirring for 1 h. Then, to this solution the Ag and Pd salts were introduced followed by dropwise addition of NaBH₄ solution at low temperature (in an ice bath). Five separate UiO-66-NH₂ solutions were arranged followed by the addition of 0.025 M of AgNO₃ (7 mL), 0.025 M PdCl₂ (7 mL), AgNO₃ + PdCl₂ (2.4 + 4.6 mL, 0.025 M), AgNO₃ + PdCl₂ (3.5 + 3.5 mL, 0.025 M), or AgNO₃ + PdCl₂ (4.6 + 2.4 mL, 0.025 M) solutions separately in five different reaction bottles. Stirring was carried out at low temperature for 1 h followed by the dropwise addition of 5 mL of NaBH₄ (0.05 M) to each reaction solution for the reduction of adsorbed AgNO₃ or/and PdCl₂. This reaction was carried out for 3 h and then the obtained suspension was

centrifuged and dried in an oven at 70 °C overnight. The dried samples were labelled as Ag@UiO-66-NH₂, Pd@UiO-66-NH₂, (1:1) Ag/Pd@UiO-66-NH₂, (1:2) Ag/Pd@UiO-66-NH₂, and (2:1) Ag/Pd@UiO-66-NH₂, respectively. The typical synthesis procedure for UiO-66-NH₂ and Ag/Pd@UiO-66-NH₂ is illustrated in Scheme 1. The details of the characterization techniques used and additional experimental procedures followed in this work are discussed in the ESI† (1. Experimental techniques).

2.1.3. Photocatalytic H₂O₂ and H₂ production. The photocatalytic performance of the synthesized samples towards H₂O₂ production was tested in an O₂ atmosphere under visible light illumination for 2 h ($\lambda > 420$ nm). A solution of 19 mL of deionized water (DI) and 1 mL of isopropanol (IPA) was mixed with 20 mg of the synthesized material. The mixture was then ultrasonicated for 10 min to completely disperse the contents. Thereafter, the resulting solution was purged with O₂ for 30 min to obtain an O₂-saturated environment, followed by light irradiation. When the reaction time was over, the suspended solution was centrifuged to obtain a clear solution. Then, 1 mL of the resultant solution was taken, to which 0.1 M KI solution (2 mL) and 0.01 M ammonium molybdate solution (0.05 mL) were added to develop a light-yellow colour in the liquid sample. Finally, the concentration of photocatalytically produced H₂O₂ was evaluated using a UV-visible spectrophotometer.

Additionally, the photocatalytic H₂ evolution ability of the synthesized photocatalysts was further studied. Herein, a 100 mL sealed quartz batch reactor was used to investigate the photocatalytic H₂ production capacity of the fabricated pristine UiO-66-NH₂ and Ag@UiO-66-NH₂, Pd@UiO-66-NH₂ and Ag/Pd@UiO-66-NH₂ composites. The produced nanomaterials (20 mg) were introduced into 20 mL of 10% MeOH-water solution and placed in the photoreactor. A xenon arc lamp (300 W, $\lambda \geq 420$ nm) was used as the visible light source and was illuminated for 1 h. The reactor's contents were stirred thoroughly to

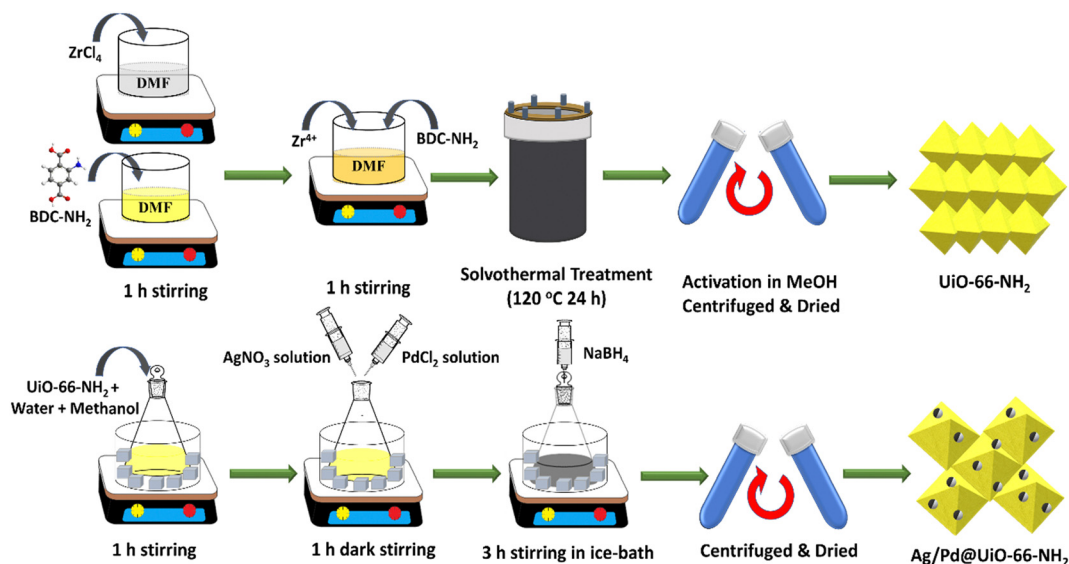

Scheme 1 Schematic representation of the preparation of UiO-66-NH₂ and Ag/Pd@UiO-66-NH₂.



avoid particle aggregation and promote uniform distribution throughout the reaction medium. Prior to placing under the Xe lamp, the solution was rigorously purged with bubbling N_2 gas for 30 minutes to eliminate dissolved gases. The evolved gaseous compounds were collected using direct water displacement and analysed using gas chromatography (GC; GC-7890B, Agilent Technologies) customised with 5 Å molecular sieves and a thermal conductivity detector (TCD).

3. Physicochemical characterization

3.1. Structural characterization

The crystallographic structure and nature of the MOF-based composite materials was studied through X-ray diffraction (XRD) method. The resulting diffraction patterns for pristine UiO-66-NH₂, Ag@UiO-66-NH₂, Pd@UiO-66-NH₂ and the UiO-66-NH₂ nanocomposites decorated with different ratios of Ag: Pd (1:1, 1:2, and 2:1 Ag/Pd@UiO-66-NH₂) are displayed in Fig. 1(a). The intense peak exhibits the outstanding crystallinity of neat UiO-66-NH₂, which is similar to previous reports.³² The diffraction pattern remained analogous even after adding Ag and Pd to the parent UiO-66-NH₂ by following the adsorption-reduction process, demonstrating the unchanged rigid framework of the MOF in the composites. Additionally, the peak intensity of UiO-66-NH₂ is slightly reduced in the synthesized composite materials, which might be due to robust interaction between the MOF and the loaded noble metal nanoparticles.²⁹ However, a small peak was observed at $2\theta = 46.3^\circ$ in the Ag@UiO-66-NH₂ and Ag/Pd@UiO-66-NH₂ composites, which corresponds to the (200) crystal plane of Ag.^{33–35} The Pd NPs decorated in Pd@UiO-66-NH₂ and Ag/Pd@UiO-66-NH₂ did not exhibit any additional diffraction peaks owing to their low weight percentage and the possibility that the diffraction peaks of the Pd metallic nanoparticles might merge with those of the UiO-66-NH₂.³⁶ Moreover, the existence of both Ag and Pd NPs in the composite was further supported by XPS, electron microscopy, colour mapping, and EDAX analysis results.

To confirm the various functional groups present in UiO-66-NH₂ and the prepared Ag and Pd nanocomposites, an FTIR study was performed and the outcomes are shown in Fig. 1(b). A double peak was observed for pristine UiO-66-NH₂ at 3340 and 3477 cm^{-1} , which are the symmetric and asymmetric stretching frequencies for -NH₂ groups, respectively. Two peaks were seen in the lower wavenumber area, at 1642 cm^{-1} and 1244 cm^{-1} , which correspond to the distinctive bending vibration of N-H and the stretching vibration for C-N of aromatic amines, respectively.³² In addition, the smaller vibrational band at 1510 cm^{-1} denotes the C=C vibration of the benzene ring.²⁸ Furthermore, the peaks observed for the vibrational frequency at the lower range, *i.e.*, around 481, 661, and 776 cm^{-1} , are connected to the asymmetric stretching of metal-(OC), O=C=O bending, and C=C stretching vibrations, respectively. FTIR analysis of the Ag- and/or Pd-nanoparticle-loaded composites exhibited an analogous pattern to that of the parent Zr-MOF, suggesting indistinguishable chemical bonding environments and functional groups present in the framework structure. This observation further corroborates the retention of the framework of UiO-66-NH₂ after noble bimetallic nanoparticle loading, as earlier seen from XRD analysis. The aforementioned FTIR spectra exhibited good concordance with the outcomes described in the literature.^{18,27,28}

The surface area (BET) and pore size (BJH) distribution of (1:2) Ag/Pd@UiO-66-NH₂ were studied using the N_2 adsorption-desorption isotherm technique. The plot of the results exhibited that a typical type-I isotherm was followed, which confirms the microporous and mesoporous nature of the obtained composite material, as depicted in Fig. S2 (ESI[†]). Furthermore, after the surface modification of the MOF with the noble metal NPs, the isotherm pattern remains unchanged but a decrease in surface area was observed as depicted in Fig. S1 (ESI[†]). This lowering of surface area (UiO-66-NH₂ = 831.49 $m^2 g^{-1}$; ³² (1:2) Ag/Pd@UiO-66-NH₂ = 681.29 $m^2 g^{-1}$) is based on the metal nanoparticle loading on the MOF surface. In short, the deposition of Ag/Pd bimetallic NPs on the UiO-66-NH₂ surface or the presence of trapped recrystallized BDC-NH₂

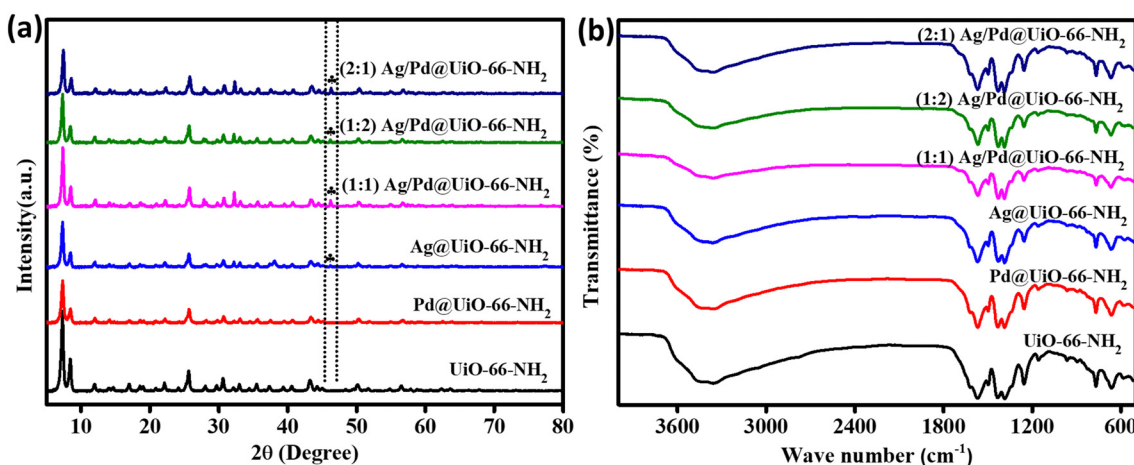


Fig. 1 (a) XRD patterns and (b) FTIR spectra for UiO-66-NH₂, Ag@UiO-66-NH₂, Pd@UiO-66-NH₂, and (1:1, 1:2, 2:1) Ag/Pd@UiO-66-NH₂.



moieties in the UiO-66-NH₂ pores may be the cause of the reduction in surface area of (1:2) Ag/Pd@UiO-66-NH₂ compared with UiO-66-NH₂.^{17,31,36} The pore volume distribution for the composite (1:2) Ag/Pd@UiO-66-NH₂ exhibits a micro-porous nature that is similar to the parent UiO-66-NH₂.

X-ray photoelectron spectroscopy (XPS) is used to determine the oxidation states of various elements present in materials. Thus, XPS analysis was carried out to elucidate the electronic valence states of several elements, such as C, N, Zr, O, Ag, and Pd, in the prepared composite materials. Fig. S2 (ESI[†]) shows the XPS survey spectra for the pristine UiO-66-NH₂ and the composite (1:2) Ag/Pd@UiO-66-NH₂, which supports the presence of N 1s, O 1s, C 1s, and Zr 3d in pristine UiO-66-NH₂ and C 1s, N 1s, O 1s, Zr 3d, Ag 3d, and Pd 3d in the composite (1:2) Ag/Pd@UiO-66-NH₂. The obtained deconvoluted peaks for UiO-66-NH₂ were located at 284.99, 286.30, and 288.96 eV in the C 1s spectrum, which corresponds to the C=C, C-NH₂, and O=C-O of the linker, respectively. The N 1s spectrum for the pristine MOF was deconvoluted into peaks at 399.52, 400.63, and 401.76 eV for the -NH₂, -NH₃⁺, and =NH₂⁺ groups of the linker, respectively. The O 1s peak was observed at 532.14 eV, which represents the Zr-O bond, and the Zr 3d spectrum was deconvoluted to give the Zr 3d_{5/2} and Zr 3d_{3/2} peaks at 183.13 and 185.61 eV, respectively, as depicted in

Table 1.¹⁸ Afterwards, the obtained deconvoluted peaks for the bimetallic (Ag/Pd)-modified UiO-66-NH₂ were positioned at 284.78, 286.2, and 288.75 eV corresponding to C=C, C-NH₂, and O=C-O for C 1s, which shows slight variation from the pristine material. The N 1s spectrum of (Ag/Pd)-modified UiO-66-NH₂ shows deconvoluted peaks at 399.37, 400.51, and 401.23 eV which represent the -NH₂, -NH₃⁺, and =NH₂⁺ groups of the linker, respectively. For O 1s, the peaks were obtained at 530.25, 531.84, and 532.63 eV, which correspond to lattice oxygen, Zr-O, and surface-adsorbed H₂O, respectively. For Zr 3d, the peaks deconvoluted into 183.01 eV and 185.39 eV, associated with Zr 3d_{5/2} and Zr 3d_{3/2}, respectively, with slight shifting relative to the peaks for pristine UiO-66-NH₂, as explained in Table 1. In the as-synthesized composite photocatalyst, the oxidation states of the noble metals Ag and Pd were deconvoluted into two peaks because of spin-orbit coupling. The deconvoluted peaks for Ag in (1:2) Ag/Pd@UiO-66-NH₂ were obtained at 368.26 and 374.28 eV for the 3d_{3/2} and 3d_{5/2} spin states, respectively. In contrast, the Pd spectrum was deconvoluted into 335.5 and 339.2 eV, representing 3d_{5/2} and 3d_{3/2}, respectively, in the (1:2) Ag/Pd@UiO-66-NH₂ composite. These obtained oxidation states of Ag and Pd validate the successful preparation of bimetallic Ag(0) and Pd(0) species from the reduction of

Table 1 XPS data for the prepared materials

| | Binding energy in eV | | | Ref. |
|------------------------------|---------------------------------------|---|---|---------------|
| Element | Carbon/C 1s | | | |
| UiO-66-NH ₂ | 284.99 | 286.30 | 288.96 | 32 and 35 |
| Ag/Pd@UiO-66-NH ₂ | 284.78 | 286.21 | 288.75 | |
| Speculation: | C=C of linker | C-NH ₂ of linker | (O=C-O) of linker | |
| Difference: | -0.21 | -0.09 | -0.21 | |
| Element | Nitrogen/N 1s | | | |
| UiO-66-NH ₂ | 399.52 | 400.63 | 401.76 | 18 and 37 |
| Ag/Pd@UiO-66-NH ₂ | 399.37 | 400.51 | 401.23 | |
| Speculation: | -NH ₂ of linker | -NH ₃ ⁺ of linker | =NH ₂ ⁺ of linker | |
| Difference: | -0.15 | -0.12 | -0.53 | |
| Element | Oxygen/O 1s | | | |
| UiO-66-NH ₂ | — | 532.14 | — | 27 and 29 |
| Ag/Pd@UiO-66-NH ₂ | 530.25 | 531.84 | 532.63 | |
| Speculation: | Lattice O | Zr-O bond | Adsorbed H ₂ O | |
| Difference: | — | -0.30 | — | |
| Element | Zirconium/Zr 3d | | | |
| UiO-66-NH ₂ | 183.13 | 185.61 | — | 28 and 29 |
| Ag/Pd@UiO-66-NH ₂ | 183.01 | 185.39 | — | |
| Speculation: | Zr ⁴⁺ (3d _{5/2}) | Zr ⁴⁺ (3d _{3/2}) | — | |
| Difference: | -0.12 | -0.22 | — | |
| Element | Silver/Ag 3d | | | |
| UiO-66-NH ₂ | — | — | — | 38–40 |
| Ag/Pd@UiO-66-NH ₂ | 368.26 | 374.28 | — | |
| Speculation: | Ag (3d _{5/2}) | Ag (3d _{3/2}) | — | |
| Difference: | — | — | — | |
| Element | Palladium/Pd 3d | | | |
| UiO-66-NH ₂ | — | — | — | 31, 33 and 37 |
| Ag/Pd@UiO-66-NH ₂ | 335.50 | 339.20 | — | |
| Speculation: | Pd (3d _{5/2}) | Pd (3d _{3/2}) | — | |
| Difference: | — | — | — | |



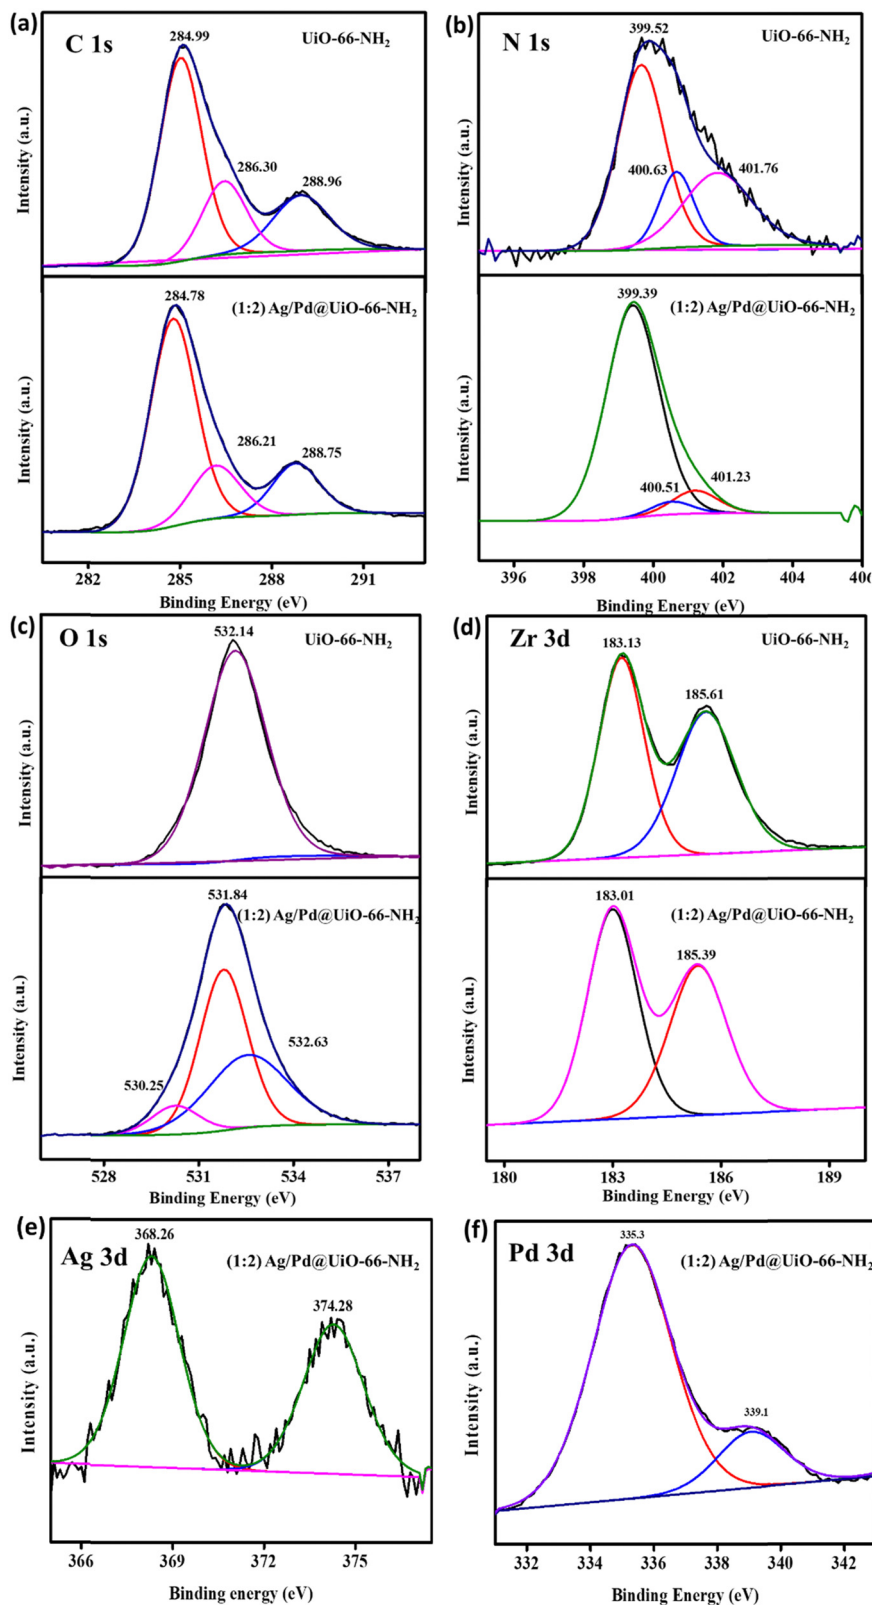


Fig. 2 (a) C 1s, (b) N 1s, (c) O 1s, (d) Zr 3d, (e) Ag 3d, and (f) Pd 3d XPS spectra for UiO-66-NH₂ and the (1:2) Ag/Pd@UiO-66-NH₂ composite.

AgNO₃⁻ and PdCl₂⁻ ions, respectively. The existence of Ag/Pd in the MOF composite was confirmed by XPS and further

corroborated by the EDS, elemental mapping, and TEM results (Fig. 2).



3.2. Morphological characterization

The morphology of the synthesized photocatalysts was characterized through FESEM and HRTEM. The clustered morphology of the composite is clearly exhibited in the FESEM image of (1 : 2) Ag/Pd@UiO-66-NH₂. Furthermore, the HRTEM image of (1 : 2) Ag/Pd@UiO-66-NH₂ exhibits the deposition of Ag/Pd on the surface of UiO-66-NH₂, which can be seen as black spots on the MOF structure.^{39,41} The lattice fringe of the parent MOF could not be clearly observed due to the sensitivity of the UiO-66-NH₂ framework towards the electron beam bombardment, but the lattice fringe was observed for (1 : 2) Ag/Pd@UiO-66-NH₂ at 0.24 and 0.22 nm, which corresponds to Ag and Pd nanoparticles and shows good agreement with the (111) plane of Ag and (111) plane of Pd in the bimetallic nanoparticles,

respectively.^{34,37} Moreover, the HRTEM analysis suggests that the bimetallic Ag/Pd NPs present in the composite have spherical morphology. The colour mapping and EDAX results for the (1 : 2) Ag/Pd@UiO-66-NH₂ composite are presented in Fig. 3(e)–(k), confirming the existence of C, N, O, Zr, Ag, and Pd, respectively. Moreover, the uniform distribution of Ag/Pd on the MOF can be seen from the elemental mapping results.

3.3. Optical and electrochemical characterization

To study the optical properties of the prepared photocatalyst materials, specifically the parent UiO-66-NH₂ and the bimetallic nanoparticle-loaded composites, UV-Vis diffuse reflectance (UV-DRS) investigation was performed, as shown in Fig. 4(a). From the DRS spectra, the neat UiO-66-NH₂ exhibits two acute

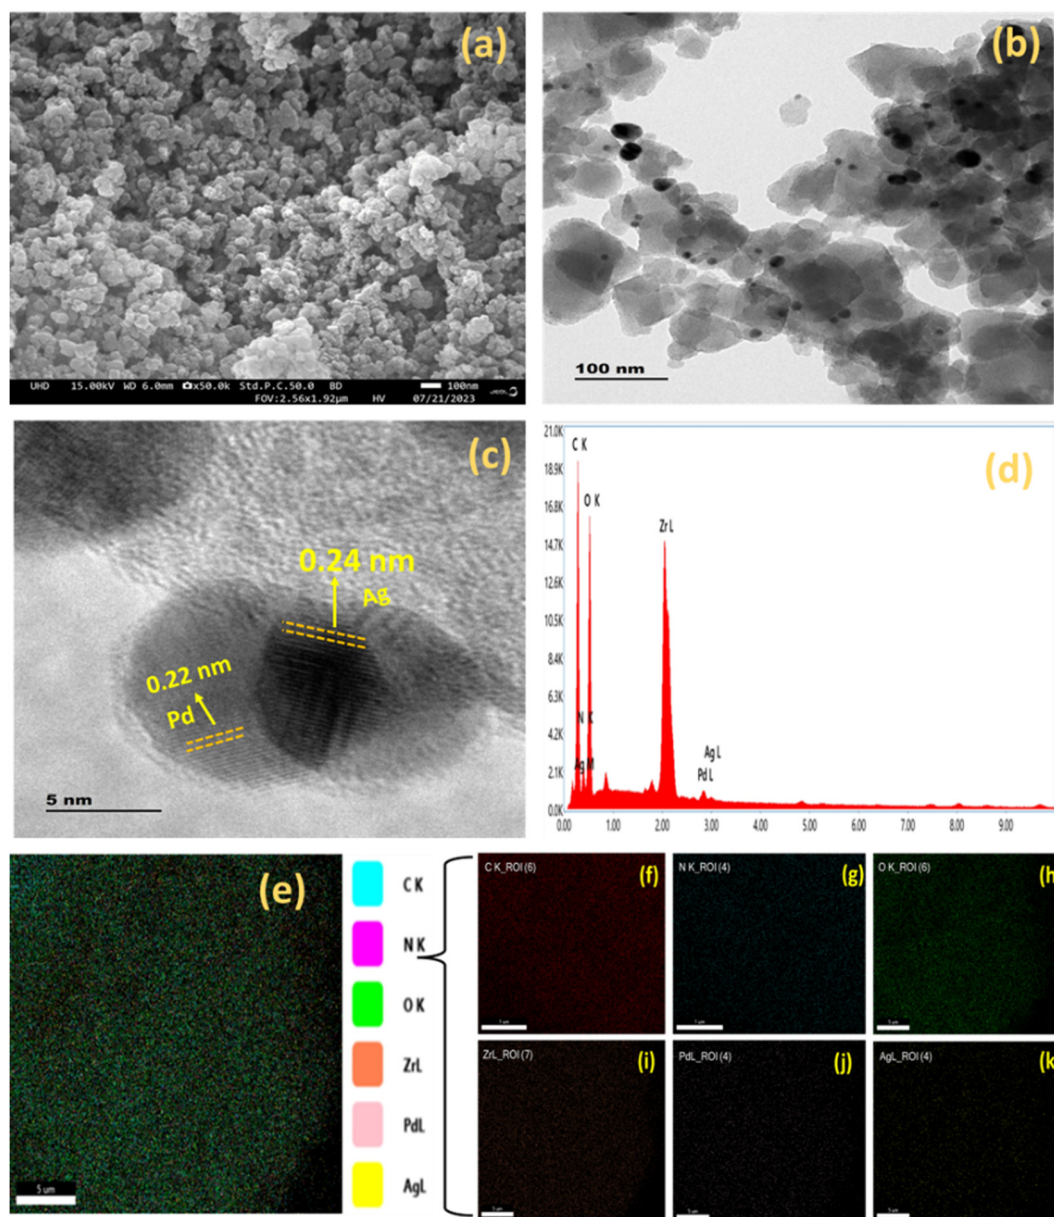


Fig. 3 (a) FESEM image of Ag/Pd@UiO-66-NH₂, (b) HRTEM image of Ag/Pd@UiO-66-NH₂, (c) HRTEM image showing lattice fringes of Ag/Pd@UiO-66-NH₂, (d) EDAX results for Ag/Pd@UiO-66-NH₂, and (e)–(k) elemental colour mapping results for Ag/Pd@UiO-66-NH₂.



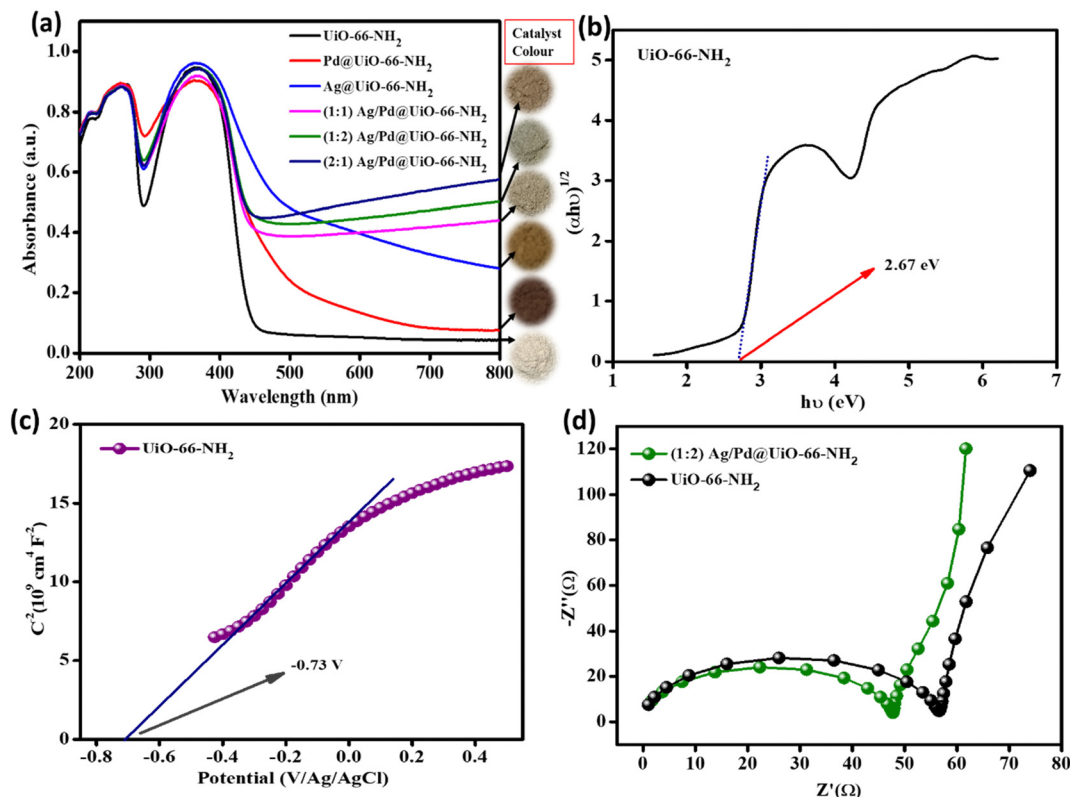


Fig. 4 (a) UV-Vis DRS spectra for the prepared samples. (b) Tauc plot for UiO-66-NH₂, (c) MS plot for parent UiO-66-NH₂, and (d) EIS plots for UiO-66-NH₂ and (1:2) Ag/Pd@UiO-66-NH₂.

bands at around 265 and 370 nm, which can be attributed to the $n-\pi^*$ transition of the lone pair of electrons of the $-\text{NH}_2$ group of the linker and the $\pi-\pi^*$ transition of the ATA linker with the Zr-oxy cluster absorption, respectively. Likewise, analogous bands to those of the parent UiO-66-NH₂ were observed for the bimetal-loaded composites, as shown in Fig. 4(a).^{18,28} However, the bimetal loading was accompanied with gradual red shifting, which signifies the more robust photon receptiveness of the composite MOFs upon the varied addition of Ag/Pd. Moreover, the deposition of metal nanoparticles led to substantial absorption beginning at 800 nm and extending into the intrinsic UiO-66-NH₂ absorption bands because of localised surface plasmon resonance (LSPR) as well as the d-d transitions of both the noble metals. Compared with individual metal deposition (Ag or Pd), this effect was significantly more noticeable in the Ag/Pd bimetallic nanoparticle-loaded MOF composites. Ag nanoparticles often exhibit a distinctive LSPR peak between 410 and 480 nm, but depending on the size, shape, and refractive index of the surrounding medium, its wavelength can vary throughout a wide range. In the current study, no strong LSPR peak was observed for Ag NPs, which is due to the small particle size and uniform dispersion of the Ag NPs,³⁴ which results in the strong absorption of the MOF composites. Pd metal exhibits strong absorbance up to 650 nm in the visible light range. The LSPR effect was not seen for the (1:1, 1:2, and 2:1) Ag/Pd@UiO-66-NH₂ composites, but the region was intensified and made wider by the Pd metal presence in

the Ag/Pd-modified UiO-66-NH₂.³⁴ So, by loading both the metals, strong visible light absorbance occurred owing to positive synergism amongst the metal nanoparticles and the MOF support. The absorption of visible light by the Ag/Pd nanoparticle-loaded MOF is considerably stronger than that of the Pd- or Ag- loaded UiO-66-NH₂ individually, demonstrating the creation of superior light-responsive bimetallic nanoparticles with respect to monometallic particles. Moreover, the material underwent an indirect transition, and for the parent UiO-66-NH₂ MOF the optical band gap obtained from the Tauc plot was around 2.67 eV, as shown Fig. 4(b), and the band gaps of all of the noble metal-loaded UiO-66-NH₂ are reduced with respect to the pristine material. So, the above results demonstrated that the loading of Ag/Pd nanoparticles improved the light-harvesting tendency compared to the monometallic or pristine MOF counterparts. By following Kubelka-Munk equation (eqn (1)), the band gap of UiO-66-NH₂ was obtained.

$$\alpha h\nu = A(h\nu - E_g)^{n/2} \quad (1)$$

The respective band edge potential of the so-formed MOF was evaluated by UV-Vis investigation and following eqn (2):

$$E_g = \text{VB} - \text{CB} \quad (2)$$

Furthermore, PL analysis was performed for the prepared pristine MOF and the Ag/Pd-loaded MOF-based photocatalysts. The PL study gives clear evidence of the separation and



recombination of the photogenerated exciton pairs, as depicted in Fig. S3 (ESI†).⁴² The peak intensity is indirectly associated with the exciton separation efficacy, *i.e.*, high intensity peaks mean a higher exciton recombination rate and low intensity peaks indicate a minimal recombination rate. From the plotted PL analysis peaks, it has been revealed that the (1:2) Ag/Pd@UiO-66-NH₂ composite exhibits a higher life span of photogenerated e⁻ and h⁺ than those of the pristine UiO-66-NH₂ and other composites.^{29,39} The aforementioned results are clearly supported by EIS measurements. Additionally, through time-resolved photoluminescence (TRPL) analysis technique, the lifespans of the photoexcited electrons of UiO-66-NH₂ and (1:2) Ag/Pd@UiO-66-NH₂ were obtained, as depicted in Fig. S4 (ESI†), which was fitted using a model biexponential eqn (3):

$$R(t) = A_1 \exp\{-t/\tau_1\} + A_2 \exp\{-t/\tau_2\} \quad (3)$$

Here, R denotes the normalized emission intensity, τ signifies the lifetime of photogenerated excitons for each component, A is the amplitude, and t is the time left after pulsed laser excitation. The essential decay and the average lifetime (τ_{avg}) of two exponentials demonstrate the inclusive TRPL character, which can be calculated using eqn (4):

$$\tau_{\text{avg}} = \frac{A_1\tau_1^2 + A_2\tau_2^2}{A_1\tau_1 + A_2\tau_2} \quad (4)$$

where τ_1 and τ_2 represent the trapping period for electrons and exciton pair generation, respectively. The fluorescence lifetimes were obtained by fitting the decay profile in Table S1 (ESI†) with the biexponential terms. Hence, the average excited lifetimes of UiO-66-NH₂ and (1:2) Ag/Pd@UiO-66-NH₂ were found to be 0.504 ns and 0.537 ns, respectively (Table S1, ESI†). So, from the result it can be clearly seen that the average lifetime of (1:2) Ag/Pd@UiO-66-NH₂ is longer, which explains the lower exciton recombination rate, thereby boosting the photocatalytic activity.

Moreover, to understand the better exciton separation efficacy of the Ag/Pd@UiO-66-NH₂ composite as compared with the parent UiO-66-NH₂, both the materials were studied by electrochemical impedance spectroscopy (EIS) under zero bias potential. In the Nyquist plots, the smaller arc radius in the high-frequency zone for the composite (1:2) Ag/Pd@UiO-66-NH₂ indicates a lower recombination rate of e⁻/h⁺ pairs as compared to that of the pristine UiO-66-NH₂. The aforementioned finding indicates that the process of charge migration in the composites was relatively smooth and the charge transfer resistance at the interface was noticeably low, which was the primary factor contributing to the composite's higher catalytic activity than that of neat UiO-66-NH₂ under identical experimental conditions, as depicted in Fig. 4(d). The EIS results further support the PL data and exhibit good correlation. In addition, current *versus* potential measurement (LSV) was carried out to study the transfer of photogenerated excitons and the photocatalytic mechanism. The analysis was performed for the parent UiO-66-NH₂, and all the Ag- and/or Pd-loaded UiO-66-NH₂ composites at 5 mV s⁻¹ in a suitable potential

range, as shown in Fig. S5 (ESI†). The pristine UiO-66-NH₂ MOF produces an anodic photocurrent, which indicates n-type characteristics. Moreover, the Ag- and/or Pd-nanoparticle-loaded composites show similar properties, possessing improved photocurrent compared to that of the pristine MOF.

MS (Mott-Schottky) analysis of the neat UiO-66-NH₂¹⁸ was performed to explain the band structure, the type of semiconductor material (p-type/n-type), and the flat band potential, as depicted in Fig. 4(c). The MS plot of pristine UiO-66-NH₂ shows a positive slope to the x -axis, which indicates the n-type nature of the parent UiO-66-NH₂. The obtained flat band potential for the material is -0.73 V. The VB and CB positions calculated using eqn (5) were 2.03 eV and -0.64 eV, respectively, *versus* the NHE (at pH = 7).

$$E_{(\text{NHE}, \text{pH}=7)} = E_{\text{Ag/AgCl}} - 0.059 \times (7 - \text{pH of the electrolyte}) + 0.198 \quad (5)$$

4. Photocatalytic performance

The photocatalytic efficiency of the prepared catalysts towards hydrogen peroxide (H₂O₂) and hydrogen (H₂) production were analysed in this study. The production of H₂O₂ in an O₂-saturated atmosphere under irradiation of visible light ($\lambda > 420$ nm) for 2 h at ambient conditions was thoroughly investigated. Moreover, in the absence of light or catalyst, no H₂O₂ production was observed, which explains that light illumination and catalysts are the primary instigators for the reaction to take place. From Fig. 5(a), the H₂O₂ production rate for UiO-66-NH₂ is 8.52 $\mu\text{mol h}^{-1}$. Amongst the prepared composite materials, (1:2) Ag/Pd@UiO-66-NH₂ exhibits the highest photocatalytic H₂O₂ production rate of 39.4 $\mu\text{mol h}^{-1}$, as shown in Fig. 5(a). H₂O₂ production rates of 18.6, 20.2, 37.3, and 34.8 $\mu\text{mol h}^{-1}$ were obtained for Ag@UiO-66-NH₂, Pd@UiO-66-NH₂, (1:1) Ag/Pd@UiO-66-NH₂, and (2:1) Ag/Pd@UiO-66-NH₂, respectively. As compared to the pristine UiO-66-NH₂, the synthesized composite materials showed significantly enhanced H₂O₂ production, which can be attributed to their superior light absorption capacity and lowering of the exciton pair recombination ability due to the presence of bimetallic Ag/Pd nanoparticles. The fabricated composite (1:2) Ag/Pd@UiO-66-NH₂ exhibits superior photocatalytic performance that is four-fold greater than that of the pristine UiO-66-NH₂ material. In addition, the reusability analysis of the composite materials showed that (1:2) Ag/Pd@UiO-66-NH₂ is photostable for up to four consecutive cycles, as illustrated in Fig. 5(b). Moreover, to study the O₂ dependency of the photocatalytic H₂O₂ production by (1:2) Ag/Pd@UiO-66-NH₂, the individual reactions were performed under Ar or O₂ gas purging, and only a small amount of H₂O₂ was generated under the Ar atmosphere, as shown in Fig. 5(c). This suggests the dependence of the photocatalytic production of H₂O₂ upon the presence of O₂. Moreover, the effect of scavengers on the H₂O₂ production is illustrated in Fig. 5(d) and discussed in detail in the subsequent



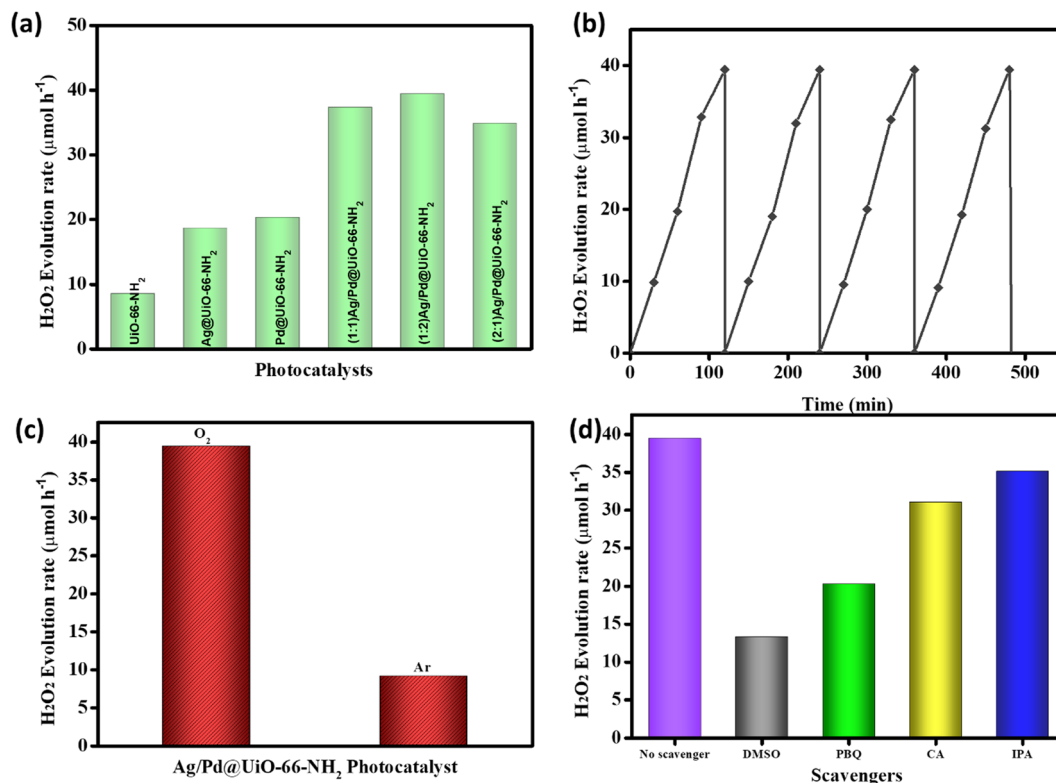


Fig. 5 (a) H₂O₂ production rate of neat UiO-66-NH₂ and Ag- and/or Pd-loaded composites. (b) Reusability test for H₂O₂ production over (1:2) Ag/Pd@UiO-66-NH₂ composite. (c) H₂O₂ production rate in different environments. (d) Effect of scavengers on the H₂O₂ production rate.

section. A comparison of the H₂O₂ production rates is given in Table S3 (ESI[†]) to show the importance of the synthesized Ag/Pd@UiO-66-NH₂ composite.^{1,43}

The photocatalytic efficacy of the synthesized samples was also measured through their H₂ evolution ability. The reaction was executed in a closed quartz batch reactor type with 100 mL volume, using 20 mg of catalyst in 20 mL of MeOH/water solution (10% v/v) at room temperature and atmospheric pressure. In the pre-irradiation stage, the reactor contents were stirred continuously to prevent the nanoparticles from settling with N₂ (gas) purging for 0.5 h to eliminate dissolved gases.

Thereafter, the light source was placed above the aqueous suspension at a distance of 8.7 cm from the bottom of the reactor. The samples were irradiated using a xenon arc lamp (300 W) with medium pressure as a source of visible light for 1 h. A GC-7890B (Agilent Technology) with 5 Å molecular sieves and a thermal conductivity detector was used to monitor the H₂ gas evolution. Blank readings were taken in the absence of a catalyst or light irradiation to prove that hydrogen evolution only occurs in the presence of both photocatalyst and light. The neat UiO-66-NH₂ exhibits a mere 115 μmol h⁻¹ of H₂ evolution because of the high recombination rate of the excitons.¹⁶

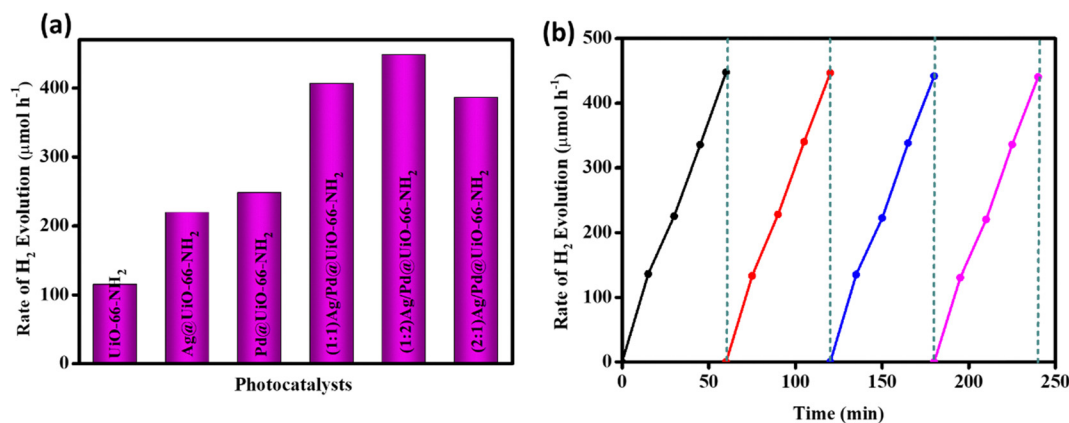


Fig. 6 (a) H₂ production rate of neat UiO-66-NH₂ and the Ag- and/or Pd-loaded composites. (b) Reusability test for H₂ production over the (1:2) Ag/Pd@UiO-66-NH₂ composite.



However, the Ag and/or Pd nanoparticle loading enhances the rate of H₂ production due to the superior absorption of visible light accompanied with enhanced charge separation and transfer. The photocatalytic H₂ evolution rates of the prepared composites Ag@UiO-66-NH₂, Pd@UiO-66-NH₂, (1:1) Ag/Pd@UiO-66-NH₂, (1:2) Ag/Pd@UiO-66-NH₂, and (2:1) Ag/Pd@UiO-66-NH₂ are 219.5, 248.1, 406.7, 448.2, and 386.3 μmol h⁻¹, respectively, as shown in Fig. 6(a). From the resultant plot it was found that (1:2) Ag/Pd@UiO-66-NH₂ shows the highest rate of photocatalytic H₂ generation, which is four times greater than that of the pristine UiO-66-NH₂. The apparent conversion efficiency (ACE) is calculated to be 3.30%, as depicted in Table S2 (ESI†). The photostability of the (1:2) Ag/Pd@UiO-66-NH₂ composite was confirmed by executing four successive cycles of H₂ evolution, with no significant change in the production rate (Fig. 6(b)) or its post-photocatalytic XRD (Fig. S5, ESI†). Moreover, ICP-OES analysis of the spent (1:2) Ag/Pd@UiO-66-NH₂ composite showed negligible change in the Ag–Pd loading percentage (Ag–Pd_{As-synthesised}: 1.4–2.4 wt% and Ag–Pd_{Post-use}: 1.25–2.26 wt%, respectively), suggesting the stability of the prepared photocatalyst. A comparison of the H₂ evolution is given in Table S4 (ESI†) to show the importance of the prepared Ag/Pd@UiO-66-NH₂ composite.

5. Mechanistic insights

The previously discussed analysis results involving physicochemical, morphological, and textural characteristics suggested the successful formation of bimetallic nanoparticle (Ag/Pd)-loaded aqueous stable UiO-66-NH₂ MOF-based photocatalysts. Moreover, the Ag/Pd noble bimetallic nanoparticle loading significantly improved the optical and electrochemical features of the pristine Zr-MOF, which is well reflected *via* the composite's enhanced photocatalytic performance. Hence, a thorough discussion of the underlying photocatalytic mechanism of Ag/Pd@UiO-66-NH₂ is imperative. Furthermore, the mechanism of photocatalytic H₂O₂ and H₂ production over the Ag/Pd@UiO-66-NH₂ surface can be posited by considering the following factors:

(i) Photoresponsive factor: the Ag/Pd bimetallic-loaded UiO-66-NH₂ composites are comparatively more photoresponsive in comparison to their pristine UiO-66-NH₂ or monometallic counterparts, as confirmed from UV-Vis DRS analysis.²⁹ This enhanced photoresponsive factor improves the photon-trapping ability, leading to the optimal formation of excitons for effective photocatalytic redox reactions.

(ii) Improved exciton antirecombination: as photoinduced excitons are the important active species towards any photocatalytic redox reaction, their improved lifetime is pivotal for superior photocatalytic performance. Here, the Ag/Pd bimetallic-loaded UiO-66-NH₂ composites have better exciton segregation tendency because of the electron-trapping ability of the bimetallic catalysts, *i.e.*, Ag/Pd.^{39,44}

(iii) Availability of active metal centres: the Ag/Pd bimetallic nanoparticle-loaded UiO-66-NH₂ composites have surplus


electron-rich noble metal-based active centres, *i.e.*, Ag/Pd nanoparticles tend to provide suitable reaction sites for the photocatalytic reduction reaction. Thus, the noble-metal-loaded MOFs show comparatively better photocatalytic performance, even with the decreased surface area.^{29,34}

(iv) LSPR effect: Ag nanoparticles can strongly absorb light because of their plasmonic properties, which is further enhanced *via* the Pd support. Therefore, in Ag/Pd-loaded UiO-66-NH₂, enhanced light absorption will occur, which ultimately helps to accelerate the photocatalytic reaction as well as exciton formation. In the present research, this approach proved beneficial towards the improved photocatalytic formation of H₂ and H₂O₂.^{34,44}

(v) Suitable band edge potential: UiO-66-NH₂ has VB = 2.03 eV and CB = -0.64 eV. This band edge potential is suitable for the studied application to show redox reactions. However, the presence of metallic components like Ag and/or Pd further enhances the reaction rate by capturing the photoexcited electrons, thereby improving their availability for the target reactions.⁴⁵

Based on these physicochemical factors, as explained on the basis of suitable instrumental characterization, the superiority in efficiency of Ag/Pd@UiO-66-NH₂ over its pristine UiO-66-NH₂ counterpart towards photocatalytic H₂ evolution and H₂O₂ production has been discussed. The UV-DRS spectra show that the absorption of Ag/Pd@UiO-66-NH₂ is significantly boosted in the visible light region, suggesting that the Ag/Pd bimetal loaded on the MOF surface plays a vital role in the higher absorption of visible light.³⁴ The co-existence of Ag/Pd was further confirmed by the XPS data and energy-dispersive X-ray (EDAX) spectra of the noble bimetallic NPs. The probable mechanism for the photocatalytic performance of Ag/Pd@UiO-66-NH₂ towards H₂O₂ and H₂ production under UV-Vis light illumination is depicted in Scheme 2. As shown from UV-Vis DRS results, the absorption of Ag/Pd@UiO-66-NH₂ is significantly increased in the visible light area, suggesting that the noble bimetal loaded on the surface of the MOF plays a significant role in the increased absorption of visible light. From the Tauc plot, the band gap of UiO-66-NH₂ was found to be 2.67 eV. Upon irradiation of visible light, the electrons from the VB of UiO-66-NH₂ get excited to the CB position. Following that, the electrons accumulate at the bimetallic surface, which acts as the electron-trapping agent and forms a Schottky barrier at the interface region between the MOF and the bimetallic NPs, which suppresses the recombination of exciton pairs. Additionally, the LSPR effect was observed due to the Ag nanoparticles, which enhanced the light-harvesting ability of the composite materials. The LSPR effect can produce a strong local electromagnetic field that can increase the energy and transfer rate of trapped electrons, facilitating easier reactions with h⁺ to produce H₂.⁴⁴ The Mott–Schottky analysis showed the VB and CB potential of UiO-66-NH₂ to be 2.03 and -0.64 eV, respectively. Following photon absorption, the electrons in the VB are energised and move to the CB of the UiO-66-NH₂, leaving a hole in the VB. As shown by the PL, TRPL, and EIS analyses, the presence of Ag/Pd bimetallic nanoparticles on the MOF



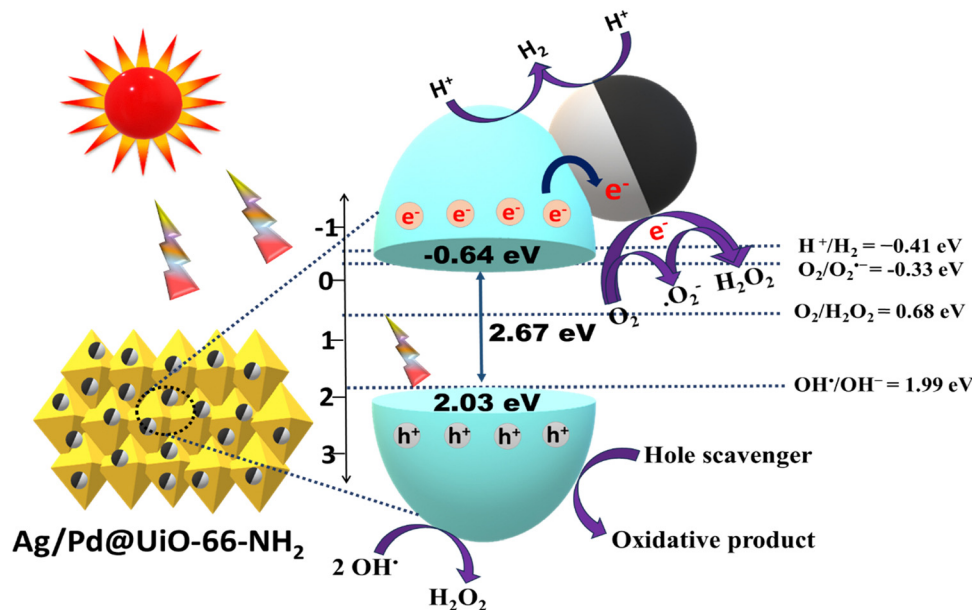


Scheme 2 Schematic representation of the mechanistic pathway for H_2O_2 and H_2 evolution by the prepared photocatalyst.


surface causes the excited electrons from the CB of the UiO-66- NH_2 to further transfer to the bimetallic surface to enhance the surface reaction more effectively and increase the exciton lifetime. When Ag/Pd is loaded onto the MOF, it helps to capture electrons from the material's surface, which enhances the photocatalytic reaction by charge carrier antirecombination in the material. Therefore, the Ag/Pd bimetallic surface essentially functions as an electron-trapping agent and aids in charge carrier separation, which is considered as the driving force for achieving the photocatalytic reaction.²⁹

Mechanistically, H_2O_2 production can be carried out *via* two pathways, *i.e.*, one-electron and two-electron pathways, as discussed subsequently. The CB potential of UiO-66- NH_2 (-0.64 eV) satisfies the H_2O_2 production as the minimum required potentials for H_2O_2 production through the oxygen reduction reaction are -0.33 eV (*via* the one-electron pathway) and 0.68 eV (*via* the two-electron pathway). Hence, the electrons transferred from the MOF surface to the bimetallic surface promote the reduction of O_2 by accepting electrons from the CB of UiO-66- NH_2 , as shown in eqn (6) and (7):^{1,3}


Single-step two-electron reduction pathway:



Two-step single-electron reduction pathway:



Moreover, the photogenerated h^+ at the VB of UiO-66- NH_2 gets trapped by the sacrificial reagent, *i.e.*, isopropanol (IPA). Additionally, the VB potential of UiO-66- NH_2 (2.03 eV) satisfies the hydroxyl radical (OH^\bullet) formation ($\text{OH}^\bullet/\text{OH}^- = 1.99$ eV *vs.* NHE). Therefore, the two OH^\bullet radicals participate in the H_2O_2 production, as shown in eqn (8):^{5,46,47}







The optimal H_2O_2 evolution rate of $39.44 \mu\text{mol h}^{-1}$ was obtained for (1 : 2) Ag/Pd@UiO-66- NH_2 . Furthermore, a recyclability test was executed to check the stability of the prepared sample and it was found the material is stable for up to four cycles, as shown in Fig. 5(b). Moreover, to check the competitiveness of the reactive species towards H_2O_2 production, scavenger tests were performed, as shown in Fig. 5(d). From the analysis, it was found that the contribution of active species follows the order; $\text{e}^- > \cdot\text{O}_2^- > \text{OH}^\bullet > \text{h}^+$ to show the role towards the formation of H_2O_2 .

Additionally, the synthesized materials were further tested towards the photocatalytic H_2 evolution reaction. A thorough investigation was conducted to explain the increased photocatalytic activity towards the evolution of H_2 gas for the Ag/Pd@UiO-66- NH_2 composite. Upon light irradiation, the electrons get excited to the CB of the MOF. These photogenerated electrons will go to the bimetallic surface due to the SPR effect of Ag NPs, which offers a driving force for H_2 evolution.^{34,39} The protons are reduced by the electrons present at the bimetallic surface, resulting in the production of molecular hydrogen. At the same time, holes present at the VB of UiO-66- NH_2 are scavenged by methanol to inhibit the exciton recombination process. Moreover, as the CB of UiO-66- NH_2 has a suitable redox potential, the photocatalytic formation of H_2 molecule can also be observed here, as shown in Scheme 2 and eqn (9)–(14). The optimum H_2 evolution rate of $448.2 \mu\text{mol h}^{-1}$ was obtained for (1 : 2) Ag/Pd@UiO-66- NH_2 . A recyclability test was also carried out to check the stability of the material and it was found the material is stable for up to four cycles, as shown in Fig. 6(b). Moreover, the post-photocatalytic XRD analysis of the used samples showed no significant changes, suggesting



framework stability of the prepared composite, which is inherited from the parent Zr-carboxylate-based MOF. The related reaction involving hydrogen evolution is represented in eqn (9)–(14).



6. Summary

Initially, the UiO-66-NH₂ framework was prepared by a solvothermal approach using Zr and aminoterephthalic acid as its constituents. This Zr-MOF is popular due to its abundant active sites, high surface area, visible-light-responsive band gap, and robust framework stability. However, the rapid rate of photo-generated exciton recombination as well as the relatively limited photon capture tendency of the pristine UiO-66-NH₂ prevents it from becoming an efficacious photocatalyst towards photocatalytic H₂O₂ and H₂ production. In an attempt to boost the photocatalytic performance of pristine UiO-66-NH₂, the framework was loaded with noble bimetallic nanoparticles that act as a co-catalyst. The Ag/Pd-co-catalyst-modified MOF was engineered *via* facile adsorption–reduction method. Physico-chemical analyses including XRD, FTIR, XPS, and BET suggested the successful loading Ag/Pd nanoparticles on the UiO-66-NH₂ surface accompanied with the preservation of the framework structure. Moreover, morphological analysis further corroborated the above results. The bimetallic nanoparticle-loaded composite (1:2) Ag/Pd@UiO-66-NH₂ exhibited significantly enhanced photocatalytic H₂ (448.2 μmol h⁻¹) and H₂O₂ (39.4 μmol h⁻¹) production capacity that is almost four-fold higher than that of the pristine UiO-66-NH₂. Additionally the photoactivity of the Ag/Pd@UiO-66-NH₂ composite was almost double those of the monometallic nanoparticle counterparts (Ag@UiO-66-NH₂ or Pd@UiO-66-NH₂). The superior output of the Ag/Pd@UiO-66-NH₂ composite can be attributed to the improved photon entrapment ability *via* Pd/Ag combinatorial support, as seen from their UV-Vis spectra. Additionally, the Ag/Pd@UiO-66-NH₂ composite displays superior exciton separation compared to the pristine UiO-66-NH₂, as demonstrated by the PL, TRPL, and EIS analyses. Mechanistically, the band structure of the parent MOF (VB: 2.03 eV and CB: -0.64 eV) makes it suitable for both H₂ and two-step H₂O₂ production. Additionally, a highly rectifying Schottky barrier with the right height is formed by bimetallic Ag/Pd nanoparticle loading, which reduces the rate of e⁻/h⁺ recombination. In addition, the Ag component enhances the visible light absorption

through the LSPR effect with the Pd support. Meanwhile, the bimetallic surface was able to readily capture photogenerated electrons from the photon-activated UiO-66-NH₂, which is further promoted by the Ag(0) and Pd(0) of the bimetallic NPs, which suppress the charge carrier recombination. In summary, the addition of Ag/Pd bimetallic NPs on the MOF surface encourages visible light absorption and electron–hole antirecombination, leading to improved H₂O₂ and H₂ production.

Conflicts of interest

The authors declare that there is no conflict of interest.

Acknowledgements

The S ‘O’ A (Deemed to be University) management are very much thankfully acknowledged for encouragement and constant support in the research work.

References

- 1 A. Ray, S. Subudhi, S. P. Tripathy, L. Acharya and K. Parida, *Adv. Mater. Interfaces*, 2022, **9**, 2201440.
- 2 H. Hou, X. Zeng and X. Zhang, *Angew. Chem., Int. Ed.*, 2020, **59**, 17356–17376.
- 3 L. Acharya, G. Swain, B. P. Mishra, R. Acharya and K. Parida, *ACS Appl. Energy Mater.*, 2022, **5**, 2838–2852.
- 4 Y. Guo, X. Tong and N. Yang, *Nanomicro Lett.*, 2023, **15**, 77.
- 5 B. P. Mishra, L. Biswal, S. Das, L. Acharya and K. Parida, *Langmuir*, 2023, **39**, 957–971.
- 6 Y. Xu, Y. Cao, L. Tan, Q. Chen and Y. Fang, *J. Colloid Interface Sci.*, 2023, **633**, 323–332.
- 7 H. Wang, L. Zhang, Z. Chen, J. Hu, S. Li, Z. Wang, J. Liu and X. Wang, *Chem. Soc. Rev.*, 2014, **43**, 5234–5244.
- 8 X. Chen, S. Shen, L. Guo and S. S. Mao, *Chem. Rev.*, 2010, **110**, 6503–6570.
- 9 J. Luo, S. Zhang, M. Sun, L. Yang, S. Luo and J. C. Crittenden, *ACS Nano*, 2019, **13**, 9811–9840.
- 10 B. Li, W. Guo, X. F. Lu, Y. Hou, Z. Ding and S. Wang, *Mater. Rep.: Energy*, 2023, **3**, 100203.
- 11 Z. Xie, W. Wang, X. Ke, X. Cai, X. Chen, S. Wang, W. Lin and X. Wang, *Appl. Catal., B*, 2023, **325**, 122312.
- 12 H. C. Zhou, J. R. Long and O. M. Yaghi, *Chem. Rev.*, 2012, **112**, 673–674.
- 13 S. P. Tripathy, S. Subudhi and K. Parida, *Coord. Chem. Rev.*, 2021, **434**, 213786.
- 14 S. Subudhi, S. P. Tripathy and K. Parida, *Inorg. Chem. Front.*, 2021, **8**, 1619–1636.
- 15 J. D. Xiao and H. L. Jiang, *Acc. Chem. Res.*, 2019, **52**, 356–366.
- 16 S. Prakash Tripathy, S. Subudhi, S. Das, M. Kumar Ghosh, M. Das, R. Acharya, R. Acharya and K. Parida, *J. Colloid Interface Sci.*, 2022, **606**, 353–366.
- 17 S. Subudhi, S. Mansingh, G. Swain, A. Behera, D. Rath and K. Parida, *Inorg. Chem.*, 2019, **58**, 4921–4934.



- 18 S. Subudhi, L. Paramanik, S. Sultana, S. Mansingh, P. Mohapatra and K. Parida, *J. Colloid Interface Sci.*, 2020, **568**, 89–105.
- 19 J. Fu and Y. Nan Wu, *Chem. – Eur. J.*, 2021, **27**, 9967–9987.
- 20 S. Subudhi, S. P. Tripathy and K. Parida, *Catal. Sci. Technol.*, 2021, **11**, 392–415.
- 21 B. Banerjee, V. Amoli, A. Maurya, A. K. Sinha and A. Bhaumik, *Nanoscale*, 2015, **7**, 10504–10512.
- 22 S. Chatterjee, S. Shaymal, M. Mukherjee, D. Halder, S. Chongdar, A. Paul and A. Bhaumik, *ChemSusChem*, 2022, **15**, e202200114.
- 23 M. Duan, L. Jiang, G. Zeng, D. Wang, W. Tang, J. Liang, H. Wang, D. He, Z. Liu and L. Tang, *Appl. Mater. Today*, 2020, **19**, 100564.
- 24 N. Sachi, A. P. Singh and M. Thirumal, *ACS Omega*, 2021, **6**, 34771–34782.
- 25 X. Sun, F. Li, Z. Wang, H. An, W. Xue and Y. Wang, *ChemCatChem*, 2021, **14**, e202101528.
- 26 R. Nazir, P. Fageria, M. Basu and S. Pande, *J. Phys. Chem. C*, 2017, **121**, 19548–19558.
- 27 S. P. Tripathy, S. Subudhi, A. Ray, P. Behera, A. Bhaumik and K. Parida, *Langmuir*, 2022, **38**, 1766–1780.
- 28 S. P. Tripathy, S. Subudhi, A. Ray, P. Behera, J. Panda, S. Dash and K. Parida, *J. Colloid Interface Sci.*, 2023, **629**, 705–718.
- 29 S. Subudhi, S. Mansingh, S. P. Tripathy, A. Mohanty, P. Mohapatra, D. Rath and K. Parida, *Catal. Sci. Technol.*, 2019, **9**, 6585–6597.
- 30 S. P. Tripathy, S. Subudhi, A. Ray, P. Behera, G. Swain, M. Chakraborty and K. Parida, *Langmuir*, 2023, **39**, 7294–7306.
- 31 S. T. Gao, W. Liu, C. Feng, N. Z. Shang and C. Wang, *Catal. Sci. Technol.*, 2016, **6**, 869–874.
- 32 S. Subudhi, G. Swain, S. P. Tripathy and K. Parida, *Inorg. Chem.*, 2020, **59**, 9824–9837.
- 33 Z. Wang, H. Lee, J. Chen, M. Wu, D. Y. C. Leung, C. A. Grimes, Z. Lu, Z. Xu and S. P. Feng, *J. Power Sources*, 2020, **466**, 228306.
- 34 I. Majeed, U. Manzoor, F. K. Kanodarwala, M. A. Nadeem, M. A. Nadeem, E. Hussain, H. Ali, A. Badshah and J. A. Stride, *Catal. Sci. Technol.*, 2018, **8**, 1183–1193.
- 35 O. Altan and E. Kalay, *Appl. Surf. Sci.*, 2022, **580**, 152287.
- 36 Y. Z. Chen, Y. X. Zhou, H. Wang, J. Lu, T. Uchida, Q. Xu, S. H. Yu and H. L. Jiang, *ACS Catal.*, 2015, **5**, 2062–2069.
- 37 J. Ma, X. Yu, X. Liu, H. Li, X. Hao and J. Li, *Mol. Catal.*, 2019, **476**, 110533.
- 38 D. Tan, J. Zhang, J. Shi, S. Li, B. Zhang, X. Tan, F. Zhang, L. Liu, D. Shao and B. Han, *ACS Appl. Mater. Interfaces*, 2018, **10**, 24516–24522.
- 39 C. Liu, Y. Zhang, J. Wu, H. Dai, C. Ma, Q. Zhang and Z. Zou, *J. Mater. Sci. Technol.*, 2022, **114**, 81–89.
- 40 J. Qin, J. Huo, P. Zhang, J. Zeng, T. Wang and H. Zeng, *Nanoscale*, 2016, **8**, 2249–2259.
- 41 N. Hintsho, L. Petrik, A. Nechaev, S. Titinchi and P. Ndungu, *Appl. Catal., B*, 2014, **156–157**, 273–283.
- 42 F. S. Hashim, A. F. Alkaim, S. J. Salim and A. H. O. Alkhayatt, *Chem. Phys. Lett.*, 2019, **737**, 136828.
- 43 Y. Peng, L. Wang, Y. Liu, H. Chen, J. Lei and J. Zhang, *Eur. J. Inorg. Chem.*, 2017, 4797–4802.
- 44 M. A. Nadeem, M. Al-Oufi, A. K. Wahab, D. Anjum and H. Idriss, *ChemistrySelect*, 2017, **2**, 2754–2762.
- 45 S. P. Tripathy, S. Subudhi, A. Ray, P. Behera, G. Swain, M. Chakraborty and K. Parida, *Langmuir*, 2023, **39**, 7294–7306.
- 46 H. Zhang and X. Bai, *Appl. Catal., B*, 2021, **298**, 120516.
- 47 X. Wang, Z. Han, L. Yu, C. Liu, Y. Liu and G. Wu, *ACS Sustainable Chem. Eng.*, 2018, **6**, 14542–14553.

