

Journal of Materials Chemistry B

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Electropolymerized molecularly imprinted polymer for selective carnosine sensing with capacitive impedimetry†

Received 00th January 20xx,
Accepted 00th January 20xx

Agnieszka Wojnarowicz,^a Piyush Sindhu Sharma,^a Marta Sosnowska,^{a,b} Wojciech Lisowski,^a Tan Phat Huynh,^{a,b} Maria Pszozna,^a Paweł Borowicz,^{a,d} Francis D'Souza,^b and Włodzimierz Kutner^{a,c}

DOI: 10.1039/x0xx00000x

www.rsc.org/

A chemosensor with a molecularly imprinted polymer (MIP) film as the recognition unit selective to a carnosine biomarker was molecularly engineered, devised and fabricated. Molecular structure of the pre-polymerization complex of the carnosine template with the carboxy and 18-crown-6 ether derivatives of *bis*(2,2'-bithien-5-yl)methane functional monomers was thermodynamically optimized by the density functional theory (DFT) at the B3LYP/6-31g(d) level. The calculated high negative Gibbs free energy change, $\Delta G = -227.4$ kJ/mol, indicated formation of a very stable complex. The solution of this complex was prepared and used for deposition of the MIP films on a Pt disk electrode or an Au electrode of the quartz crystal resonator by potentiodynamic electropolymerization. Subsequently, the carnosine template was extracted from the MIPs with 0.1 M NaOH, as confirmed by the differential pulse voltammetry (DPV), X-ray photoelectron spectroscopy (XPS), and Raman spectroscopy measurements. For carnosine sensing, impedimetric capacity (CI) measurements were performed under flow-injection analysis (FIA) conditions resulting in the limit of detection of 20 μM (at $S/N=3$). This limit implied readiness of the chemosensor for carnosine determination in clinical samples. Due to multiple modes of carnosine binding to MIP recognizing sites, the CI chemosensor was found to be more selective to carnosine than to its common interferences including anserine, carcine and histidine. Advantageously, the imprinting factor, determined by piezoelectric microgravimetry (PM), was high equalling, 14.9.

Introduction

Carnosine **1** (Scheme 1a) is a dipeptide composed of L-histidine and β -alanine. Carnosine, L-anserine, and hemocarnosine are three representative histidine-containing dipeptides widely distributed in human body. There, carnosine is synthesized by the ATP-dependent carnosine synthetase enzyme.^{1,2} The highest carnosine concentrations are found in skeletal muscle tissues, stomach, kidney, and cardiac muscle.^{3,4,5,6} as well as in brain neurons, olfactory bulbs, and glial cells.^{7,8,9} Carnosine plays several important roles in human body. First, it is a chelator of metal ions including copper, zinc, and iron.^{10,11} Second, its buffering activity helps controlling the intracellular hydrogen ion concentration.^{12,13} Moreover, carnosine is known as an antioxidant,^{14,15,16,17} anti-glycation agent,^{18,19,20} and hydroxyl radical scavenger.²¹ Therefore, it is administered as a potential supplement of diet or medicine in treatment of many diseases including diabetes,²² vascular dementia,¹² neurological disorders (e.g., Alzheimer disease,²³ Parkinson's disease²⁴) as well as ocular diseases, e.g., the cataract disease²⁵ and diabetic retinopathy²⁶.

Carnosine is used as a biomarker, i.e., a biological molecule occurring in body fluids or tissues whose concentration, 18.6 \pm 16.8 μM in urine²⁷ and 20-180 mg carnosine/(100 g wet weight skeletal muscle tissue),²⁸ reflects the conditions of processes or reactions for treatment. Carnosine level determination in serum can help indicating serum carnosinase deficiency (*carnosinemia*), which is autosomal recessive metabolic disorder^{29,30,31} caused by the CNDP1 gene mutation. This disorder is manifested by the increased carnosine concentration in urine.³² Importantly, detection of carnosine can help diagnosing the Alzheimer and Parkinson diseases^{23,1} as well.

For carnosine determination, mostly flow analytical techniques are used including high-performance liquid chromatography (HPLC),^{33,34} hydrophilic interaction liquid chromatography (HILIC),³⁵ and capillary electrophoresis (CE).^{36,37} The carnosine limit of detection reached by these techniques is high. However, all of them are expensive and require trained personnel to operate them. They are time-consuming and labor-demanding because of a long analysis time and additional necessary sample preparation steps. For instance, electrophoresis requires derivatization of carnosine prior determination.^{36,37} Towards sensing of carnosine, a recent report described differential pulse voltammetric (DPV) determination of this dipeptide at the μM concentration level.³⁸ Unfortunately, the sensor suffers from low selectivity with respect to the anserine structural analogue of carnosine. Moreover, a cross-reactive chemosensor array was developed by combining transition-metal complexes with six different fluorescent dyes for selective determination of carnosine

^a Institute of Physical Chemistry (IPC PAS), Kasprzaka 44/52, 01-224 Warsaw, Poland. E-mail: psharma@ichf.edu.pl; wkutner@ichf.edu.pl

^b Department of Chemistry, University of North Texas, Denton, 1155, Union Circle, #305070, TX 76203-5017, USA. Email: Francis.Dsouza@unt.edu

^c Faculty of Mathematics and Natural Science, School of Sciences, Cardinal Stefan Wyszyński University in Warsaw, Wycickiego 1/3, 01-938 Warsaw, Poland

^d Institute of Electron Technology, Al. Lotników 37/46, 02-668 Warsaw, Poland

†Electronic Supplementary Information (ESI) available: XPS and Raman spectra of MIP-carnosine before and after carnosine extraction, and theoretical and experimental Raman spectra of the MIP film. See DOI: 10.1039/x0xx00000x

and hemocarnosine.³⁹ However, this chemosensor array required a specialized hardware to operate and time-consuming sample pretreatment.

The chemosensors with dedicated molecularly imprinted polymers (MIPs) as recognition units for selective and reversible interactions with carnosine are expected to overcome these determination disadvantages. Molecular imprinting is a procedure leading to the formation of molecular cavities in a polymer matrix with a memory of the size, shape, and orientation of the template molecules used for imprinting. Often, an analyte itself initially serves as the template.⁴⁰ Therefore, the MIP use for chemosensor fabrication has been increasing for the last few decades.^{41,42,43} Mostly, MIPs were prepared by free-radical polymerization of vinyl or acrylic functional monomers derivatized with recognition sites.⁴⁴ However, literature on the MIP application for carnosine determination is scarce.⁴⁵ The polymer imprinted with carnosine suffered from a long-time preparation procedure and it was not used as a recognition unit of a chemosensor.⁴⁵

In the present study, we used carnosine-templated MIPs as recognition units of carnosine chemical sensors. For the imprinting, we utilized *bis*(2,2'-bithiophene) derived functional monomers developed in our laboratories due to their availability with variety of recognition sites.⁴⁶ The monomers used in the present study are composed of two parts. One part is an electroactive *bis*(2,2'-bithiophene) moiety capable of electropolymerization while the other is a recognition site capable of interacting with the available binding sites of the carnosine template.⁴⁷ Advantageously, thickness and morphology of the *bis*(2,2'-bithiophene) based MIPs prepared by electropolymerization are easily controlled.^{48,49,50} Moreover, this electropolymerization does not require using any initiator and, additionally, chemical stability of the resulting MIPs is high. Accordingly, two functional monomers were chosen, namely, 4-*bis*(2,2'-bithien-5-yl)methylbenzoic acid **2** and *bis*(2,2'-bithienyl)benzo[18-crown-6]methane **3**. Structure of the pre-polymerization complex of the functional monomers and the carnosine template was optimized with quantum chemistry computing. A mixture of solvents was carefully composed to dissolve all components of the pre-polymerization complex, and then to enable electropolymerization of this complex. The MIP films were deposited on two different signal transducers. These included a Pt disk electrode for capacity measurements by impedimetry and an Au film coated quartz crystal resonator (Au-QCR) for piezoelectric microgravimetry (PM). Moreover, these films were deposited on the Au film coated glass slides for spectroscopic analyses and microscopic imaging. Subsequent extraction of the carnosine template from the MIP films resulted in fabrication of recognition units of the chemosensor.

Experimental

Reagents and chemicals

L-Carnosine **1** (Scheme 1a), L-anserine nitrate salt, L-histidine, carnosine dihydrochloride, and acetonitrile "for electrochemistry" were purchased from Sigma-Aldrich. Tetrabutylammonium

perchlorate, (TBA)ClO₄, was from Fluka. Lithium nitrate was provided by CIECH S.A. Sodium hydroxide, potassium nitrate, and potassium hexacyanoferrate(II) were purchased from POCH S.A. Functional monomers **2** and **3** (Scheme 1a) were prepared, as described previously.^{49,51}

Instrumentation and procedures

The electropolymerization under potentiodynamic conditions, cyclic voltammetry (CV), and differential pulse voltammetry (DPV) measurements were performed using an SP-300 BioLogic potentiostat controlled by the EC-Lab BioLogic software. A 1-mm diameter Pt disk electrode, a 5-mm diameter gold film electrode deposited on an Au-QCR, and a glass slide coated with Au films were used as the working electrodes. A Pt wire and an Ag/AgCl electrode was used as the counter and reference electrode, respectively.

Extraction of the carnosine template from the MIP films was controlled by DPV in the potential range of 0.0 to 0.60 V. For that purpose, the 0.1 M K₄Fe(CN)₆ redox probe in 0.1 M KNO₃ was used.

Before and after carnosine template extraction, the deposited MIP film was imaged with atomic force microscopy (AFM) using a Nanoscope V microscope controlled by a MultiMode[®] 8 controller of Bruker. The tapping mode was used for this imaging, which embraced the (0.5 × 0.5) μm² area. For this imaging, the MIP films were deposited on the Au film coated glass slides. These slides were cleaned with toluene, and then with acetone before deposition of the MIP films.

The X-ray photoelectron spectroscopy (XPS) spectra were recorded on a PHI 5000 VersaProbe™ (ULVC-PHI) scanning ESCA microprobe using monochromatic Al K_α radiation (*hν*=1486.4 eV). The XPS data were generated by a 100-μm diameter X-ray beam and collected from 250 μm² irradiated area. The high-resolution (HR) XPS spectra were collected with a hemispherical analyzer at the pass energy of 23.5 eV, energy step of 0.1 eV, and photoelectron take off angle of 45° with respect to the surface plane. The CASA XPS software was used to evaluate the XPS data. The background was subtracted using the Shirley method and peaks were fitted using the mixed Gaussian-Lorentzian method. The binding energy of the Au 4f_{7/2} peak (*BE* = 84.0 eV) was chosen as an internal reference. The samples for XPS and Raman spectroscopic measurements were prepared in the same way as that for imaging with AFM.

The Raman spectroscopy spectra were obtained with the InVia confocal Renishaw system using a Leica microscope with the Peltier-cooled 1024×256 pixel CCD detector. Signals were collected using 100× Leica air objective (NA = 0.85) and dispersed by 1200 grooves/mm grating. The spectral resolution was 5-6 cm⁻¹ and wavelength accuracy was 2 cm⁻¹. The excitation source was the He-Ne laser (623.8 nm) and the total number of scans for each spectrum was 600. The laser power was 50-500 μW on the sample. The spectra were background corrected using cubic-spline interpolation. The experimental Raman spectra were compared with the theoretical spectra. The theoretical spectra were calculated for **3** and the complex of **1** and **3** using the density functional theory (DFT) at the B3LYP/6-31G level with the harmonic approximation, with the Gaussian 09 software.⁵² The analysis of theoretical spectra was

performed using Vibrational Energy Distribution Analysis (VEDA).^{53,54} The background was subtracted and spectra were mathematically reconstructed using the Opus 6.5 and Fityk 0.9.8 software, respectively.⁵⁵ The theoretical and experimental spectra were compared with the SPESCA software using weighted linear regression.⁵⁶

The absorption FTIR spectra of the carnosine template **1**, functional monomer **3**, and the complex of **1** with **3** in potassium bromide (KBr) pellets were recorded with a Vertex 80 V Fourier Transform Infrared (FTIR) Spectrometer of Bruker with the DTGS detector. The samples were prepared by mixing of **1**, functional monomer **3**, and complex of **1** and **3** (mixture of **1** and **3** was dissolved in the acetonitrile : water solution and allowed to evaporate the solvent, thus obtaining a powder) with a KBr powder, respectively, and press to form pellets. Then, 256 scans of the FTIR spectra were recorded at 0.6 cm⁻¹ resolution. For comparison, theoretical IR spectra were calculated using the same method as that mentioned above for calculation of theoretical Raman spectra.

The PM measurements were carried out under flow-injection analysis (FIA) and stagnant-solution conditions using a flow cell⁵⁷ and an EQCM 5710⁵⁸ quartz crystal microbalance (QCM) operated by the EQCM 5710-S2 software, respectively, and an EP-20A potentiostat, all of the Institute of Physical Chemistry PAS. The resonance frequency was measured with 0.1-Hz resolution using 14-mm diameter AT-cut plano-plano 10-MHz resonance frequency Au-QCRs with the ~100 μm thick circular Au film electrodes evaporated over the Ti underlayer on both sides of the resonator. However, the test solution wetted only one crystal side. In the FIA measurements, the flow cell was connected to a 922 model Quartz Crystal Analyzer of Seiko EG&G and an SP-300 potentiostat of BioLogic, both controlled by the EC-Lab BioLogic software. A 0.1 M LiNO₃ solution, used as the carrier liquid in FIA, was pumped with the flow rate of 35 μL/min through the flow cell by a model 78/100 syringe pump of KD Scientific. The 100-μL samples were injected with a 7725i model rotary six-port valve of Rheodyne. The carnosine analyte or its interferences were dissolved in the solution of the same composition as that of the carrier solution.

The impedimetric capacity measurements were performed under the same FIA conditions as those adopted for the PM measurements. The capacity measurements were carried out using a large-volume (35 mL) radial-flow thin-layer electrochemical cell⁵⁹ filled with the 0.1 M LiNO₃ carrier solution. The Pt working electrode was axially mounted above the inlet capillary orifice at the (capillary outlet)-to-electrode distance of 300 μm. A Pt wire loop and an Ag/AgCl electrode was used as the auxiliary and reference electrode, respectively. The applied frequency and potential were kept constant at 20 Hz and 0.50 V vs. Ag/AgCl, respectively.

Polymer film preparation

The MIP film was deposited from the pre-polymerization complex solution of carnosine and functional monomers by electropolymerization under potentiodynamic conditions. This solution contained acetonitrile and water in the volume ratio of 9 : 1. Moreover, it was 0.1 mM in carnosine, 0.3 mM in **2**, 0.1 mM in **3** and

0.1mM in the (TBA)ClO₄ supporting electrolyte. The electropolymerization was carried out over the potential range of 0 to 1.40 V vs. Ag/AgCl using the Pt disk electrode, the Au-QCR, and the Au film coated glass slides at the scan rate of 50 mV/s. Thickness of the deposited polymer film was controlled with the number of potential cycles and the optimum thickness⁶⁰ was reached within five cycles. After the electropolymerization was completed, the electrode coated with the MIP-carnosine film was rinsed with abundant acetonitrile to remove excess of the supporting electrolyte. Then, the carnosine template was extracted from the film by extraction with 0.1 M NaOH for 30 min at room temperature. Completeness of this removal was confirmed by the DPV and XPS measurements.

Moreover, a non-imprinted polymer (NIP) film was prepared as a control. It was deposited under the solution conditions same as those for the MIP film deposition, however, in the carnosine absence.

Quantum chemistry calculations

Structure of the pre-polymerization complex, in vacuum, of the carnosine template **1** and both functional monomers **2** and **3** was optimized and values of thermodynamic functions were calculated using DFT at the B3LYP/6-31G(d) level with the Gaussian 09 software.⁵²


Results and discussion

Molecular modeling of interactions between binding sites of the carnosine template and recognition sites of functional monomers

Structure of the pre-polymerization complex of the carnosine template and both functional monomers was optimized by computational modeling (Scheme 1). In Scheme 1a, the structural formula of this complex is proposed. In this complex (Scheme 1b), hydrogen atoms 106, 107, and 108 of the amine group of **1** interact with the 18-crown-6 moiety of **3**. Here, the crown ether moiety of **3** plays the role of a host moiety including the -NH₃⁺ guest moiety of **1**. The hydrogen atom 103 and the oxygen atom 101 of **1** are complementarily paired with the oxygen atom 198 and the hydrogen atom 200 of the carboxy group of **2'**, respectively, forming two distinct hydrogen bonds. The same interactions are characteristic of atoms of the peptide bond of **1**. That is, the hydrogen atom 93 and the oxygen atom 104 of carnosine are complementarily paired with the oxygen atom 244 and the hydrogen atom 246 of **2**, respectively. The hydrogen atom 82 of the imidazole substituent of **1** forms a hydrogen bond with the oxygen atom 152 of the carbonyl group of **2''**. Table 1 summarizes results of the calculated Gibbs free energy change, ΔG, due to possible interactions of different recognition sites of functional monomers with complementary binding sites of the carnosine template. Calculations of the change of thermodynamic functions corresponding to formation of a complex of **1**, **2**, and **3** of the 1 : 3 : 1 stoichiometry and the optimized structure, resulted in a substantial total negative change of the free energy, ΔG = -227.4 kJ/mol (Table 1). This relatively high ΔG gain indicated the possibility of formation of a stable (multi host)-carnosine complex. In the

optimized structure of carnosine, there are seven possible binding sites. Unfortunately, one site, i.e., unprotonated nitrogen of the imidazole ring, is not accessible to any recognition site of the functional monomers because of steric hindrance. Nevertheless, the computational DFT modeling indicated, advantageously, strong six-point binding of the carnosine template.

The total ΔG change because of formation of the carnosine complex was compared with the ΔG for histidine-(functional monomers) complex where histidine was chosen as its interference because the histidine moiety is a part of the carnosine dipeptide. For that purpose, computational modeling was performed. The complex structure was frozen in such a way that the recognition sites of the functional monomers were left unfrozen.⁴⁶ After that, carnosine and histidine molecules were allowed to equilibrate, separately, with the frozen molecular cavity. The total free energy change for the frozen carnosine complex was, $\Delta G = -347.01$ kJ/mol. However, this change for the frozen histidine complex was nearly half that, $\Delta G = -183.85$ kJ/mol. These results confirmed that the molecular cavity of the designed MIP preferentially bound the carnosine dipeptide.

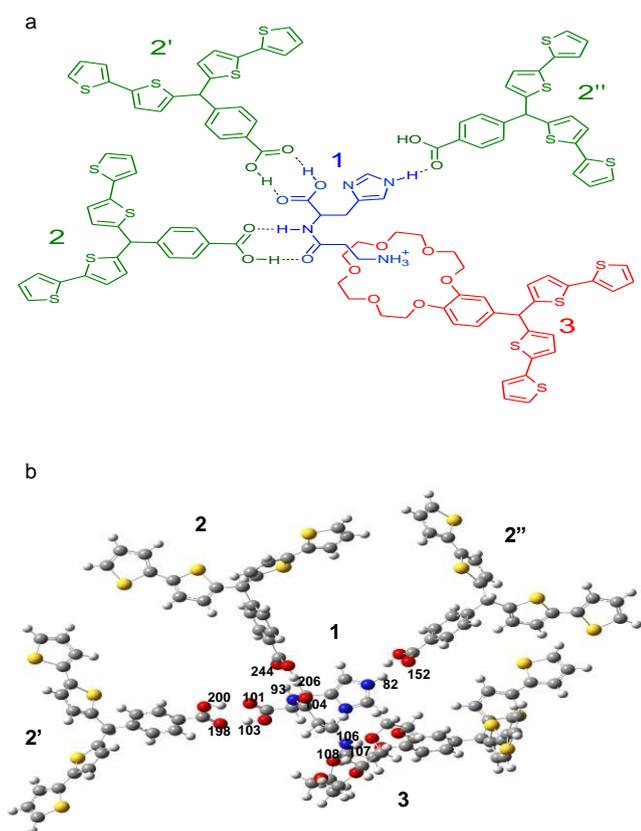

Scheme 1 (a) The proposed structural formula of the pre-polymerization complex of the carnosine template **1** with functional monomers **2** and **3**, and (b) the B3LYP/6-31g(d) optimized structure of the complex. Gray, red, blue, yellow, and white spheres represent carbon, oxygen, nitrogen, sulfur, and hydrogen atoms, respectively.

Infrared spectroscopic characterization of pre-polymerization complex formation in solution

Several studies confirmed that oxygen atoms of crown ethers interact with hydrogen atoms of protonated primary and secondary amines. In effect, inclusion complexes are formed.⁶¹⁻⁶⁵ We performed IR measurements to verify host-guest interactions between the carnosine template **1** with the 18-crown-6 derivatized bis(bithiophene) functional monomer **3**. Accordingly, in Fig. S1, IR spectra of carnosine, functional monomer **3**, and the complex of carnosine-(functional monomer) in KBr are presented. Fig. S1a shows two peaks at 1492 and 1644 cm⁻¹ that are assigned to bending of the N-H bond⁶⁶. These peaks are shifted to higher wavenumbers of 1607 and 1734 cm⁻¹, respectively, in the spectrum of the complex (Fig. S1c) because of interactions of oxygen atoms of the crown ether moiety of **3** with hydrogen atoms of **1**. Apparently, N-H...O hydrogen bonds were formed confirming inclusion complexation. The presence of mentioned peaks and their shift to higher wavenumbers correspond to calculated theoretical IR spectra (blue vertical lines, in Fig. S1).

Deposition of MIP-carnosine films on different working electrodes

With respect to the optimized structure of the pre-polymerization complex, the solution of **1**, **2**, and **3** with the mole ratio of 1 : 3 : 1, respectively, was prepared for electropolymerization. Unfortunately, the carnosine template is insoluble in acetonitrile. Therefore, 10% water was first used to dissolve all the components. Finally, (TBA)ClO₄ was added to satisfy the electropolymerization requirement of sufficiently high ionic strength. The MIP-carnosine film was deposited on three different working electrodes, viz., the Pt disk electrode (for capacity measurements), the Au-QCR (for PM measurements), and the Au film coated glass slide (for AFM imaging).

Table 1 The Gibbs free energy change (ΔG) corresponding to formation of a complex of the carnosine template with functional monomers.

Functional monomer	Type of binding	ΔG (kJ/mol)
Carboxylic acid derivative 2	Hydrogen bond	-35.8
Carboxylic acid derivative 2'	Hydrogen bond	-42.8
Carboxylic acid derivative 2''	Hydrogen bond	-22.2
[18-crown-6] ether derivative 3	Inclusion interactions	-178.2
Pre-polymerization complex of the carnosine template 1 and functional monomers 2 , 2' , 2'' , and 3		-227.4

The anodic peak of electropolymerization of functional monomers **2** and **3** appeared in the first cycle at ~1.10 V (Fig.1). In the next cycle, this peak was shifted to the higher potential value of ~1.20 V. In subsequent cycles, it decreased with the growth of thickness of the deposited film. This decrease indicated the increase of resistance of the deposited film. Apparently, the MIP-carnosine film plays the role of a barrier inhibiting the charge shuttling between

the electrode surface and the redox species in solution, thus hindering the electrode redox reaction.

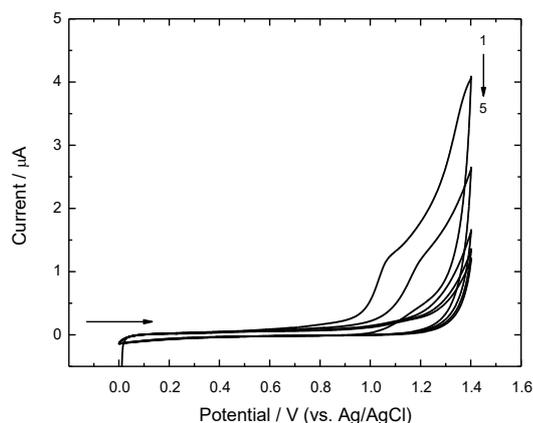


Fig. 1 Potentiodynamic curves for 0.1 mM **1**, 0.3 mM **2**, 0.1 mM **3** in 0.1 M (TBA)ClO₄ in the acetonitrile-water solution (9 : 1, v : v) on the 1-mm diameter Pt disk electrode for 5 potential cycles at the potential scan rate of 50 mV/s.

Moreover, the above electropolymerization procedure was used for deposition of the MIP-carnosine film on the Au-QCRs for PM measurements (Fig. 2). In the first potential cycle, the anodic peak appeared at ~1.20 V (Fig. 2a). This sharp peak converted into broad peak with a hump at ~1.0 in the second cycle. Importantly, in subsequent cycles these two peaks merged to form one broad peak at more positive potentials.⁶⁷ Moreover, the anodic current decreased with each cycles. A cathodic peak was present at ~0.60 V. It increased in the first three cycles, and then decreased. Deposition of the MIP-carnosine film on the Au-QCR was accompanied by a decrease of the resonance frequency (Fig. 2b) indicating the increase of the Au-QCR mass. This frequency decrease was lower in each consecutive cycle. Moreover, the film deposition caused only minor dynamic resistance decrease (Fig. 2c) indicating only negligible changes in the film viscosity and density.

Extraction of the carnosine template from the MIP-carnosine film

A strongly basic solution, used for extraction of the carnosine template, caused deprotonation of carnosine ($pK_1 = 2.76$ of -COOH, $pK_2 = 6.72$ of N-H in the imidazole ring, and $pK_3 = 9.32$ of -NH₂ of the β -alanine residue,⁶⁸). This deprotonation resulted in decomposition of the supramolecular complex of the crown ether moiety of **3** with the -NH₂ group of **1**. Moreover, it led to rupture of all hydrogen bonds because of formation of carboxylates and imidazolate, and hence electrostatic repulsion of the carboxylate recognition sites of **2'** and **2''** by the carboxylate binding sites of carnosine.

To confirm completeness of the extraction, the DPV experiments exploiting the "gating effect" were performed (Fig. 3). In these experiments, K₄[Fe(CN)₆] was used as the redox probe. The bare electrode was freely accessible for the Fe(CN)₆⁴⁻/Fe(CN)₆³⁻ electrode reaction (curve 1 in Fig. 3). However, this probe could not approach the electrode surface coated by the MIP-carnosine film, as manifested by no current flow (curve 2 in Fig. 3). The carnosine

template extraction from the film emptied molecular cavities, and hence facilitated diffusion of the probe to the electrode surface through the MIP film (curve 3-5 in Fig. 3). After 20 min, the DPV current peak increase for redox probe was slowed down. We extracted the MIP film for additional 10 min for complete template removal. The completeness of extraction was confirmed by XPS measurements (Fig. S2).

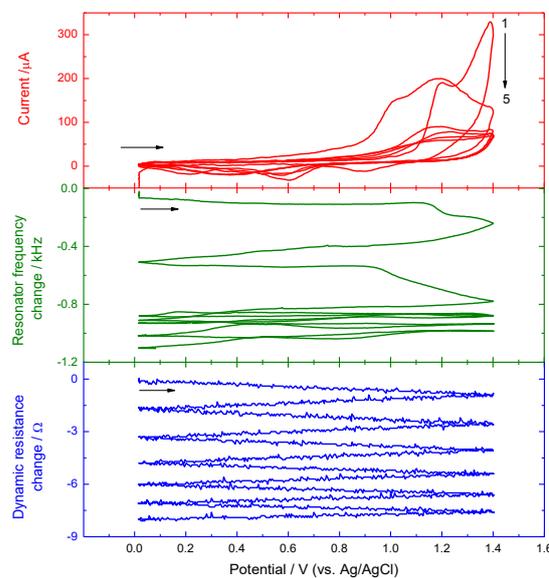


Fig. 2 Simultaneously recorded curves of the potential dependence of (a) current as well as the change of (b) resonant frequency and (c) dynamic resistance for deposition of an MIP-carnosine film by potentiodynamic electropolymerization at the 10-MHz Au-QCR. The solution composition was the same as that on Fig. 1.

In the XPS spectra, the N 1s electron binding energy was chosen as a marker for confirming the presence, and then absence of the carnosine template in the MIP film before and after extraction, respectively (Figures S2a and S2b). The composed band at ~400 eV corresponds to the electrons of nitrogen atoms at different positions in the carnosine template imprinted in the polymer. The deconvoluted spectrum shows two peaks, i.e., one at 399.12 and the other at 401.42 eV. These peaks can be assigned to electron of the nitrogen atom of the histidine residue or the nitrogen atom of the peptide bond, and primary aliphatic amine, -NH₃⁺,⁶⁹ respectively. It is difficult to distinguish bands of the nitrogen atoms of the imidazole ring and those of the peptide bond because of peak overlapping. Nevertheless, the presence of the N 1s peaks (Fig. S2a) confirms template imprinting in the MIP. Then, the absence of these peaks after carnosine template extraction (Fig. S2b) proves completeness of this extraction.

The Raman spectra of the carnosine powder as well as MIP films before and after template extraction were recorded (Fig. S3). In Fig S3a, there are peaks characteristic of carnosine. At 1407 and 630 cm⁻¹, there are peaks corresponding to in-plane deformation vibrations and a strong peak responsible for stretching vibration of

the COO⁻ moiety, respectively. Peaks at 1433, 1469, 1498, 1572, and 1666 cm⁻¹ can be assigned to vibrations of the imidazole ring.⁷⁰ A peak corresponding to the C-H in-plane deformation vibration in the imidazole ring is seen at 990 cm⁻¹.⁷⁰ Fig. S3b presents the Raman spectrum of the MIP film before removal of the carnosine template. This spectrum shows peaks ascribed to vibrations related to thiophenes and carnosine.⁶⁶ That is, the peak at 1441 cm⁻¹ corresponds to stretching vibrations of the imidazole ring. After extraction of the carnosine template (Fig. S3c) intensity of this peak decreased, thus confirming removal of this template.

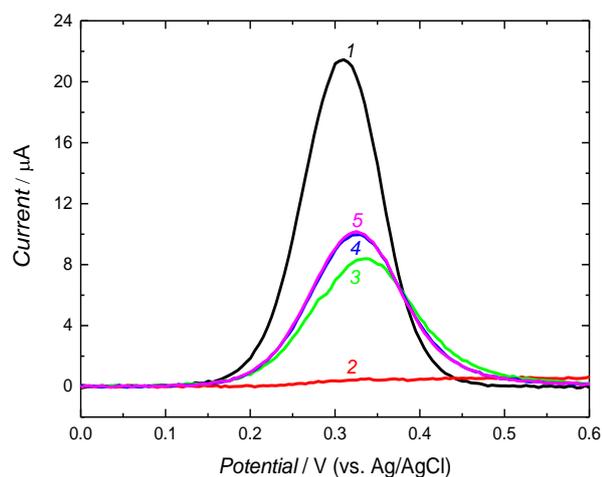


Fig. 3 The DPV curves for 0.1 M K₄[Fe(CN)₆] in 0.1 M KNO₃ on (1) the bare Pt disk electrode as well as for the Pt disk electrode coated with the MIP-carnosine film (2) before and after extraction of the carnosine template with 0.1 M NaOH for (3) 10 min, (4) 20 min, and (5) 30 min.

The Raman spectra of the MIP film are dominated by peaks originating from the C-C stretching vibrations. Fig. S4 shows peaks corresponding to vibrations of the N-H...O bonds formed between **1** and **3**. A weak peak at 1686 cm⁻¹ observed before template extraction (Fig. S4a) disappeared after the extraction (Fig. S4b). Blue vertical lines represent theoretically calculated normal modes. They can be assigned to vibrations of the NH₃⁺ group of carnosine interacting with oxygen atoms of the crown ether moiety of **3**. In the red frame (Fig. S4a), the scaled peak at 1645 cm⁻¹ (experimental 1710 cm⁻¹) contains 50% of the H-N-H bending vibration. Formation of hydrogen bonds of the guest-host complex resulted in pushing this peak toward higher scaled Raman shift of 1660 cm⁻¹ (experimental 1742 cm⁻¹). The difference between these peaks for the experimental data is 40-41 cm⁻¹ while our calculations predicted the shift of 32 cm⁻¹ in view of the literature 29-cm⁻¹ calculated shift.⁷¹

Surface morphology of the MIP-carnosine film

The AFM imaging of the MIP-carnosine film before (Fig. 4a) and after (Fig. 4b) carnosine template extraction revealed that the film was homogenous and composed of small grains of ~10 nm in diameter. These grains provided large surface area (Fig. 4a and 4b), thus

maximizing interactions of the MIP with the analyte molecules. Before template extraction, thickness of 240(±24) nm and roughness of 1.5(±0.1) nm of the MIP-carnosine film were determined. Interestingly, this thickness was practically the same after carnosine template removal, then being 229(±24) nm. Therefore, possible polymer swelling and contribution of this swelling to the measured capacity is that way excluded.

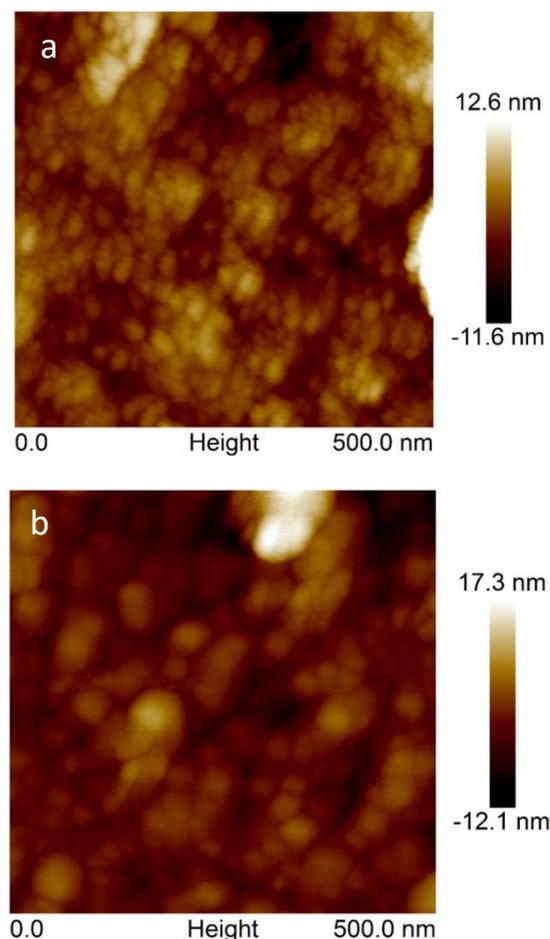


Fig. 4 The atomic force microscopy (AFM) images of the MIP-carnosine film deposited over Au film-coated glass slides of the surface area of (0.5×0.5) μm² (a) before and (b) after extraction of the carnosine template.

Determination of carnosine using capacity measured by impedimetry under FIA conditions

A Pt disk electrode coated with the carnosine-extracted MIP-carnosine film was used for capacity impedimetric measurements of carnosine determination under FIA conditions. The impedance measurements were performed at the direct current potential offset of 0.50 V and the alternating current potential amplitude of 10 mV. During measurements, frequency was kept constant, $f = 20$ Hz. At this low frequency, the MIP film coated electrode mainly reveals capacitive properties. This capacity was low at low potential and it rapidly increased with the potential increase. However, the capacity was low again when the polymer was completely oxidized. Therefore, the potential of 0.50 V was selected as an optimized

potential in these measurements.⁷² Importantly, this potential was much lower than that of oxidation of the thiophene polymer. The double-layer capacity was calculated from the equation

$$Z'' = \frac{1}{\omega C_{dl} A} \quad (1)$$

where, Z'' is the imaginary component of impedance, ω is the angular velocity equal to $2\pi f$, and A is the electrode surface area. Rearrangement of Eq. 1 results in

$$C_{dl} = \frac{1}{2\pi f A Z''} \quad (2)$$

According to Eq. 2, capacity can readily be determined from the Z'' measurement at constant and sufficiently low frequency.

The capacity increased after injection of the carnosine analyte solutions, and then decreased to form peaks (Fig. 5). Concentration of the carrier electrolyte solution was kept high (0.1 M LiNO₃) to minimize contribution of the diffuse-layer capacity to the total capacity measured. Therefore, this capacity increase was related to the increase of the compact part of the double layer. Hence, the Helmholtz model of the double layer could be adopted. In this model, capacity solely depends upon the electric permittivity, ϵ , and thickness of the compact part of the double layer, d , as Eq. 3 describes⁷³

$$C_{dl} = \frac{\epsilon \epsilon_0}{dA} \quad (3)$$

The decrease of thickness of the compact part of the double layer and/or the increase of relative permittivity caused by the appearance of the carnosine ions in the MIP may result in the C_{dl} increase. As expected, capacity of the imprinted polymer film increased with the increase of the concentration of the injected carnosine analyte sample solution (Fig. 5).

The linear dynamic concentration range of at least 0.1 to 0.75 mM determined (Inset in Fig. 5) was characterized by the linear regression equation of the calibration plot of C_{dl} ($\mu\text{F cm}^{-2}$) = $0.01378(\pm 5.61 \times 10^{-4})$ ($\mu\text{F cm}^{-2} \text{ mM}^{-1}$) $C_{\text{carnosine}}$ (mM) + $8.0 \times 10^{-4}(\pm 2.33 \times 10^{-4})$ ($\mu\text{F cm}^{-2}$) with the correlation coefficient of 0.992 and sensitivity of $0.01378(\pm 5.61 \times 10^{-4}) \mu\text{F cm}^{-2} \text{ mM}^{-1}$. At $S/N = 3$, the limit of detection reached 20 μM carnosine.

For selectivity studies, structural analogues of carnosine, including anserine, carbinine, and histidine, were chosen. Our chemosensor appeared appreciably selective toward these analogues (Inset to Fig. 5). That is, sensitivity to carnosine was ~ 38 times that to anserine being $3.59 \times 10^{-4}(\pm 2.81 \times 10^{-4}) \mu\text{F cm}^{-2} \text{ mM}^{-1}$ and over 100 times that to carbinine, which was $4.24 \times 10^{-8}(\pm 1.31 \times 10^{-4}) \mu\text{F cm}^{-2} \text{ mM}^{-1}$. However, selectivity to histidine, which is a part of the carnosine dipeptide analyte, was ~ 3 times lower than that to carnosine equaling $0.0047(\pm 2.38 \times 10^{-4}) \mu\text{F cm}^{-2} \text{ mM}^{-1}$. Not surprisingly, molecular cavities created for carnosine were sufficiently big to accommodate small histidine molecules. Moreover, our quantum chemistry calculations confirmed this result (Section 3.1, above). That is, the strength of histidine binding by the

molecular cavity imprinted with carnosine was half that of carnosine binding.

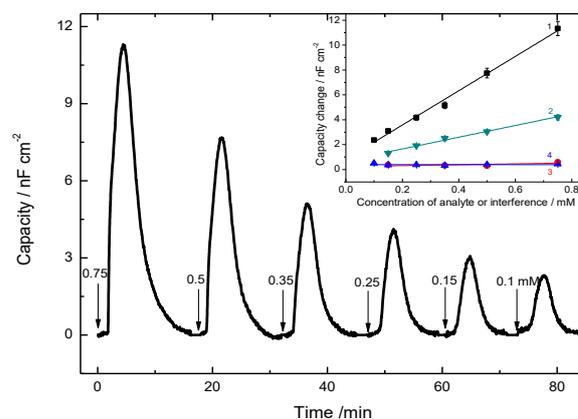


Fig. 5 The capacity change with time under the FIA conditions for the 100- μL injections of carnosine in 0.1 M LiNO₃ at the applied potential of 0.5 V vs. Ag/AgCl and frequency of 20 Hz for the 1-mm diameter Pt disk electrode coated with the carnosine template extracted MIP-carnosine film. The carnosine concentration is indicated at each peak. Inset is calibration plots on the Pt disk electrode coated with the carnosine template extracted MIP-carnosine film for (1) carnosine and its structural analogues of (2) L-histidine, (3) L-anserine and (4) carbinine. The flow rate of 0.1 M LiNO₃, used as the carrier solution, was 35 $\mu\text{L}/\text{min}$.

Determination of the imprinting factor using piezoelectric microgravimetry under the FIA conditions

The PM technique was used to determine the imprinting factor of the MIP film. For that purpose, the Au-QCR coated with the MIP-carnosine film was mounted in the EQCM 5610 holder, and then carnosine was determined under the FIA conditions. The change of the resonant frequency, Δf , is related to the change of mass, Δm , of a rigid film deposited on the Au-QCR surface, as described by the Sauerbrey relation (Eq. 4)

$$\Delta f = \frac{-2f_0^2 \Delta m}{A_{ac} \sqrt{\rho_q \mu_q}} \quad (4)$$

Here, f_0 is a resonant frequency (10 MHz), A_{ac} is an acoustically active resonator surface area (0.1963 cm²), on which the MIP-carnosine film is deposited, ρ_q is a quartz density (2.648 g cm⁻³), and μ_q is a shear modulus of quartz for the AT-cut crystal (2.947×10^{11} g s⁻¹ cm⁻¹).

The frequency decreased, and then increased to its baseline after each consecutive injection of the carnosine sample solutions of different concentrations (Fig. 6). This frequency behavior indicated binding of the carnosine molecules by the empty cavities of the film, and then releasing these molecules with excess of the carrier solution. Apparently, the absolute change of the resonant frequency was higher the higher was the carnosine concentration.

The linear dynamic concentration range of 0.75 to 5 mM obtained was characterized by the linear regression equation of Δf (Hz) = $-12.79(\pm 0.63)$ (Hz mM⁻¹) $C_{\text{carnosine}}$ (mM) - $16.12(\pm 1.78)$ (Hz) with

the correlation coefficient and sensitivity of 0.993 and $-12.79(\pm 0.63)$ Hz mM^{-1} , respectively.

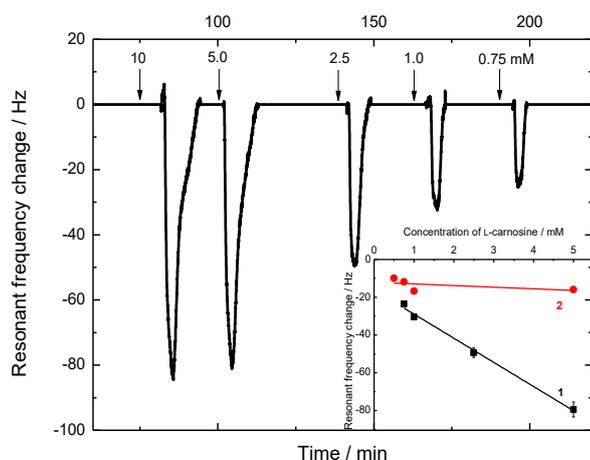


Fig. 6 The resonant frequency change with time under the FIA conditions for 100- μL injections of carnosine in 0.1 M LiNO_3 on the Au-QCR coated with the carnosine template extracted MIP-carnosine film. The flow rate of 0.1 M LiNO_3 , used as the carrier solution, was 35 $\mu\text{L}/\text{min}$. The carnosine concentration is indicated at each peak. Inset represents the PM calibration curves for carnosine on the Au-QCR coated with the film of (1) MIP and (2) NIP.

Similar measurement was performed for the NIP film coated Au-QCR. Sensitivity of this control chemosensor toward carnosine within the linear concentration range of 0.5 to 5 mM was low. The obtained calibration curve obeyed the linear regression equation of Δf (Hz) = $-0.86(\pm 0.89)$ (Hz $\text{mM}^{-1}) C_{\text{carnosine}}$ (mM) - $12.09(\pm 2.30)$ (Hz). The imprinting factor, determined as the ratio of sensitivity to carnosine of the MIP film to that of the NIP film was as high as 14.9.

Conclusions

The carnosine template was successfully imprinted in a conducting polymer matrix. Computational modeling appeared to be a powerful tool in predicting formation of a stable pre-polymerization complex of the carnosine template with suitably selected *bis*(2,2'-bithien-5-yl)methane derived functional monomers. Electropolymerization under potentiodynamic conditions enabled depositing MIP films on different electrodes including the Pt disk electrode and the Au-QCR. Moreover, it allowed controlling the film thickness and its morphology. The MIP-carnosine film, applied as a recognition unit of the capacity impedimetric chemosensor, proved to be a sensitive tool for fast and selective determination of carnosine with appreciable detectability of 20 μM . Owing to the presence of multiple modes of binding of the analyte with the MIP recognition sites, the fabricated chemosensor manifested high selectivity to structural carnosine analogues including anserine and carinine as well as histidine, the latter being a part of the carnosine molecule. With its high (14.9) imprinting factor, our chemosensor is suitable for clinical analysis directed toward early diagnosis of diseases associated with the carnosine abnormal concentration in body fluids.

Acknowledgements

The present research was financially supported by the Polish National Centrum of Science through the Grants numbers NCN 2011/03/D/ST4/02596 to P.S.S. and NCN 2014/15/B/N27/01011 to W.K. as well as by US National Science Foundation grant number 1401188 to F.D.

Notes and references

1. F. Bellia, G. Vecchio and E. Rizzarelli, *Molecules*, 2014, **19**, 2299-2329.
2. K. Bauer, *Neurochem. Res.*, 2005, **30**, 1339-1345.
3. A. R. Hipkiss, J. E. Preston, D. T. M. Himswoth, V. C. Worthington, M. Keown, J. Michaelis, J. Lawrence, A. Mateen, L. Allende, P. A. M. Eagles and N. J. Abbott, *Ann. N. Y. Acad. Sci.*, 1998, **854**, 37-53.
4. C. A. Hill, R. C. Harris, H. J. Kim, B. D. Harris, C. Sale, L. H. Boobies, C. K. Kim and J. A. Wise, *Amino Acids*, 2007, **32**, 225-233.
5. G. Begum, A. Cunliffe and M. Leveritt, *Int. J. Sport Nutr. Exerc. Metab.*, 2005, **5**, 493-514.
6. R. C. Harris, J. A. Wise, K. A. Price, H. J. Kim, C. K. Kim and C. Sale, *Amino Acids*, 2012, **43**, 5-12.
7. A. Neidle and J. Kandra, *Brain Res.*, 1974, **80**, 359-364.
8. L. Bonfantia, P. Peretto, S. D. Marchisc and A. Fasoloc, *Prog. Neurobiol.*, 1999, **59**, 333-353.
9. F. L. Margolis, *Science*, 1974, **184**, 909-911.
10. E. J. Baran, *Biochemistry (Moscow, Russ. Fed.)*, 2000, **65**, 789-797.
11. P. Q. Trombley, M. S. Horning and L. J. Blakemore, *Biochemistry (Moscow, Russ. Fed.)*, 2000, **65**, 807-816.
12. D. Mizuno and M. Kawahara, *J. Vasc. Med. Surg.*, 2014, **2**, 146.
13. H. Abe, *Biochemistry (Moscow, Rus. Fed.)*, 2000, **65**, 757-765.
14. R. Kohen, Y. Yamamoto, K. C. Cundy and B. N. Ames, *PNAS*, 1988, **85**, 3175-3179.
15. E. A. Decker and H. Faraji, *JAACS*, 1990, **67**, 650-652.
16. S. Zhou and E. A. Decker, *J. Agric. Food Chem.*, 1999, **47**, 51-55.
17. M. A. Babizhayev, M. C. Seguin, J. Gueyne, R. P. Evstigneeva, E. A. Ageyeva and G. A. Zheltukhina, *Biochem. J.*, 1994, **304**, 509-516.
18. H. Yan and J. J. Harding, *Biochim. Biophys. Acta*, 2005, **1741**, 120-126.
19. N. W. Seidler, G. S. Yeargans and T. G. Morgan, *Arch. Biochem. Biophys.*, 2004, **427**, 110-115.
20. V. P. Reddy, M. R. Garrett, G. Perry and M. A. Smith, *Sci. Aging Knowl. Environ.*, 2005, **2005**, 12.
21. M. Tamba and A. Torreggiani, *Int. J. Radiat. Biol.*, 1999, **75**, 1177-1188.

22. K. Nagai, A. Nijima, T. Yamano, H. Otani, N. Okumra, N. Tsuruoka, M. Nakai and Y. Kiso, *Exp. Biol. Med.*, 2003, **228**, 1138-1145.
23. A. R. Hipkiss, *J. Alzheimers Dis.*, 2007, **11**, 229-240.
24. A. Boldyrev, T. Fedorova, M. Stepanova, I. Dobrotvorskaya, E. Kozlova, N. Boldanova, G. Bagyeva, I. Ivanova-Smolenskaya and S. Illarioshkin, *Rejuvenation Res.*, 2008, **11**, 821-827.
25. F. Attanasio, S. Cataldo, S. Fisichella, S. Nicoletti, V. G. Nicoletti, B. Pignataro, A. Savarino and E. Rizzarelli, *Biochemistry*, 2009, **48**, 6522-6531.
26. F. Pfister, E. Riedl, Q. Wang, F. v. Hagen, M. Deinzer, M. C. Harmsen, G. Molema, B. Yard, Y. Feng and H.-P. Hammes, *Cell. Physiol. Biochem.*, 2011, **28**, 125-136.
27. Y. Tsuruta, K. Maruyama, H. Inoue, K. Kosha, Y. Date, N. Okamura, S. Eto and E. Kojima, *J. Chromatogr. B*, 2010, **878**, 327-332.
28. M. C. Jackson and J. F. Lenney, *Inflamm. Res.*, 1996, **45**, 132-135.
29. T. L. Perry, S. Hansen, B. Tischler, R. Bunting and K. Berry, *N. Engl. J. Med.*, 1967, **277**, 1219-1227.
30. I. Everaert, Y. Taes, E. D. Heer, H. Baelde, A. Zutinic, B. Yard, S. Sauerhöfer, L. Vanhee, J. Delanghe, G. Aldini and W. Derave, *Am. J. Physiol. Renal. Physiol.*, 2012, **302**, F1537-F1544.
31. P. L. Hartlage, R. A. Roesel, A. G. Eller and F. A. Hommes, *J. Inherit. Metab. Dis.*, 1982, **5**, 13-14.
32. S. M. Willi, in *NORD guide to rare disorders*, ed. N. O. f. R. Disorders, Lippincott Williams & Wilkins, USA, 1 edn., 2003, p. 435.
33. J. J. O'Dowd, D. J. Robins and D. J. Miller, *Biochim. Biophys. Acta* 1988, **967**, 241-249.
34. Y. J. Park, S. L. Volpe and E. A. Decker, *J. Agric. Food Chem.*, 2005, **53**, 4736-4739.
35. L. Mora, M. A. Sentandreu and F. Toldrá, *J. Agric. Food Chem.*, 2007, **55**, 4664-4669.
36. Y. Huang, J. Duan, H. Chen, M. Chen and G. Chen, *Electrophoresis*, 2005, **26**, 593-599.
37. S. Zhao, Y. Huang, M. Shi, J. Huang and Y.-M. Liu, *Anal. Biochem.*, 2009, **393**, 105-110.
38. M. Jozanović, M. Medvidović-Kosanović and M. Sak-Bosnar, *Int. J. Electrochem. Sci.*, 2015, **10**, 6548-6557.
39. S. Rochat, J. Gao, X. Qian, F. Zaubitzer and K. Severin, *Chem. Eur. J.*, 2010, **16**, 104-113.
40. C. Alexander, H. S. Andersson, L. I. Andersson, R. J. Ansell, N. Kirsch, I. A. Nicholls, J. O'Mahony and M. I. J. Whitcombe, *J. Mol. Recognit.*, 2006, **19**, 106-180.
41. T.-P. Huynh, A. Wojnarowicz, M. Sosnowska, S. Srebnik, T. Benincori, F. Sannicolò, F. D'Souza and W. Kutner, *Biosens. Bioelectron.*, 2015, **70**, 153-160.
42. P. S. Sharma, M. Dabrowski, K. Noworyta, T.-P. Huynh, C. B. KC, J. W. Sobczak, P. Pieta, F. D'Souza and W. Kutner, *Anal. Chim. Acta*, 2014, **844**, 61-69.
43. K. Haupt and K. Mosbach, *Chem. Rev.*, 2000, **100**, 2495-2504.
44. P. S. Sharma, F. D'Souza and W. Kutner, *TrAC Trends Anal. Chem.*, 2012, **34**, 59-77.
45. B. Okutucu and F. Zihnioglu, *Mater. Sci. Eng., C*, 2012, **32**, 1174-1178.
46. T.-P. Huynh, P. S. Sharma, M. Sosnowska, F. D'Souza and W. Kutner, *Prog. Polym. Sci.*, 2015, **47**, 1-25.
47. P. S. Sharma, A. Pietrzyk-Le, F. D'Souza and W. Kutner, *Anal. Bioanal. Chem.*, 2012, **402**, 3177-3204.
48. A. Pietrzyk, W. Kutner, R. Chitta, M. E. Zandler, F. D'Souza, F. Sannicolò and P. R. Mussini, *Anal. Chem.*, 2009, **81**, 10061-10070.
49. A. Pietrzyk, S. Suriyanarayanan, W. Kutner, R. Chitta and F. D'Souza, *Anal. Chem.*, 2009, **81**, 2633-2643.
50. A. Pietrzyk, S. Suriyanarayanan, W. Kutner, R. Chitta, M. E. Zandler and F. D'Souza, *Biosens. Bioelectron.*, 2010, **25**, 2522-2529.
51. T.-P. Huynh, K. Bikram, W. Lisowski, F. D'Souza and W. Kutner, *Bioelectrochemistry*, 2013, **93**, 37-45.
52. M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. M. Jr., J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, J. M. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, Ö. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, *Gaussian 09*, Gaussian, Inc: Wallington CT, 2009.
53. M. H. Jamróz, *Vibrational energy distribution analysis, Spectroscopy and molecular modeling group, Institute of nuclear chemistry and technology*, 2004-2010.
54. M. H. Jamróz, *Spectrochim. Acta A Mol. Biomol. Spectrosc.*, 2013, **114**, 220-230.
55. M. Wojdyr, *J. Appl. Crystallogr.*, 2010, **43**, 1126-1128.
56. M. H. Jamróz, SPESCA, *Spectroscopy and molecular modeling group, Institute of nuclear chemistry and technology*, 2014.
57. A. Kochman, A. Krupka, J. Grissbach, W. Kutner, B. Gniewinska and L. Nafalski, *Electroanalysis*, 2006, **18**, 2168-2173.
58. W. Koh, W. Kutner, M. T. Jones and K. M. Kadish, *Electroanalysis*, 1993, **5**, 209-214.
59. B. Soucaze-Guillous and W. Kutner, *Electroanalysis*, 1997, **9**, 32-39.

ARTICLE

Journal Name

60. A. Pietrzyk, S. Suriyanarayanan, W. Kutner, E. Maligaspe, M. E. Zandler and F. D'Souza, *Bioelectrochemistry*, 2010, **80**, 62-72.
61. M. Hiraoka, *Crown ethers and analogue compounds*, Elsevier, 1992.
62. T. Koide and K. Ueno, *J. Chromatogr. A*, 2001, **909**, 305-315.
63. R. Kuhn, *Electrophoresis*, 1999, **20**, 2605-2613.
64. M. Schafer, *Angew. Chem. Int. Ed.*, 2003, **42**, 1896-1899.
65. J. W. Steed and J. L. Atwood, *Supramolecular Chemistry*, Wiley and Sons, Ltd., United Kingdom, 2 edn., 2009.
66. G. Socrates, *Infrared and Raman characteristic group frequencies*, Wiley, New York, 2001.
67. D. C. Apodaca, R. B. Pernites, R. R. Ponnampati, F. R. D. Mundo and R. C. Advincula, *ACS Appl. Mater. Interfaces*, 2011, **3**, 191-203.
68. A. A. Boldyrev, G. Aldini and W. Derave, *Physiol. Rev.*, 2013, **93**, 1803-1845.
69. T. Matsukura, T. Takahashi, Y. Nishimura, T. Ohtani, M. Sawada and K. Shibata, *Chem. Pharm. Bull.*, 1990, **38**, 3140-3146.
70. A. Torreggiani, M. Tamba and G. Fini, *Biopolymers*, 2000, **57**, 149.
71. N. S. Myshakina, Z. Ahmed and S. A. Asher, *J. Phys. Chem. B*, 2008, **112**, 11873-11877.
72. N. Mermilliod and J. Tanguy, *J. Electrochem. Soc.*, 1986, **133**, 1073-1079.
73. A. J. Bard and L. R. Faulkner, *Electrochemical methods fundamentals and application*, Wiley India, 2 edn., 2010.

Page 10 Journal of Materials Chemistry B

Functional monomers are designed for development of molecular cavities selective for the carnosine dipeptide.

