

Cite this: *Chem. Sci.*, 2018, 9, 5564

# Revealing the unusual role of bases in activation/deactivation of catalytic systems: O–NHC coupling in M/NHC catalysis†

Victor M. Chernyshev,<sup>a</sup> Oleg V. Khazipov,<sup>a</sup> Maxim A. Shevchenko,<sup>a</sup>  
Andrey Yu. Chernenko,<sup>a</sup> Alexander V. Astakhov,<sup>a</sup> Dmitry B. Eremin,<sup>b</sup>  
Dmitry V. Pasyukov,<sup>a</sup> Alexey S. Kashin<sup>b</sup> and Valentine P. Ananikov<sup>\*,ab</sup>

Numerous reactions are catalyzed by complexes of metals (M) with N-heterocyclic carbene (NHC) ligands, typically in the presence of oxygen bases, which significantly shape the performance. It is generally accepted that bases are required for either substrate activation (exemplified by transmetalation in the Suzuki cross-coupling), or HX capture (e.g. in a variety of C–C and C-heteroatom couplings, the Heck reaction, C–H functionalization, heterocyclizations, etc.). This study gives insights into the behavior of M(II)/NHC (M = Pd, Pt, Ni) complexes in solution under the action of bases conventionally engaged in catalysis (KOH, NaOH, *t*-BuOK, Cs<sub>2</sub>CO<sub>3</sub>, K<sub>2</sub>CO<sub>3</sub>, etc.). A previously unaddressed transformation of M(II)/NHC complexes under conditions of typical base-mediated M/NHC catalyzed reactions is disclosed. Pd(II) and Pt(II) complexes widely used in catalysis react with the bases to give M(0) species and 2(5)-oxo-substituted azoles *via* an O–NHC coupling mechanism. Ni(NHC)<sub>2</sub>X<sub>2</sub> complexes hydrolyze in the presence of aqueous potassium hydroxide, and undergo the same O–NHC coupling to give azolones and metallic nickel under the action of *t*-BuOK under anhydrous conditions. The study reveals a new role of NHC ligands as intramolecular reducing agents for the transformation of M(II) into “ligandless” M(0) species. This demonstrates that the disclosed base-mediated O–NHC coupling reaction is integrated into the catalytic M/NHC systems and can define the mechanism of catalysis (molecular M/NHC vs. “NHC-free” cocktail-type catalysis). A proposed mechanism of the revealed transformation includes NHC–OR reductive elimination, as implied by a series of mechanistic studies including <sup>18</sup>O labeling experiments.

Received 23rd March 2018

Accepted 19th May 2018

DOI: 10.1039/c8sc01353e

rsc.li/chemical-science

## Introduction

Complexes of transition metals with N-heterocyclic carbene (NHC) ligands are commonly applied as catalysts for a variety of C–C and C-heteroatom bond formations, C–H functionalizations, the Mizoroki–Heck reaction, atom-economic additions, and many other transformations.<sup>1</sup> Fine organic synthesis and its industrial applications are indispensable for obtaining complex molecular structures of pharmaceutical substances, natural product substitutes, smart materials, and molecular electronic components, among many other examples of paramount significance.<sup>2</sup> The universal application of M/NHC

complexes in catalysis is attributed to the great stability of M–NHC bonds and the high variability of the steric and electronic parameters of NHC ligands, which allows effective tuning of the catalyst activity.<sup>1,3</sup>

The vast majority of practically relevant M/NHC catalyzed reactions are conducted in the presence of bases, including strong bases like alkali metal hydroxides or alkoxides.<sup>1–5</sup> The bases play important roles of capturing HX from the catalytic cycle, facilitating the transmetalation process, and inducing the formation of nucleophilic reagents.<sup>4b,6</sup> The nature of the base can significantly shape the catalytic performance of the M/NHC system in terms of activity and selectivity.<sup>1–7</sup>


Several published studies of catalytic systems consider the effects of the base on the metal center of the catalyst and reveal few additional roles of bases in metal-catalyzed reactions. Participation of bases in ligand exchange, with its effects on the activity and selectivity, is a well-established phenomenon. For example, coordination of *tert*-butoxide anions to nickel promotes the oxidative addition of H<sub>2</sub> in C–O activation reactions.<sup>8</sup> Coordination of tertiary amines apparently blocks the β-hydride elimination in the Mizoroki–Heck reaction, and this

<sup>a</sup>Platov South-Russian State Polytechnic University (NPI), Prosveschenya 132, Novocherkassk, 346428, Russia

<sup>b</sup>Zelinsky Institute of Organic Chemistry, Russian Academy of Sciences, Leninsky Prospekt 47, Moscow, 119991, Russia. E-mail: val@ioc.ac.ru

† Electronic supplementary information (ESI) available: Additional experimental data for reaction mechanisms and stoichiometry, copies of NMR spectra and Raman spectra, GC-MS and ESI-MS data, and FE-SEM/EDS data. See DOI: 10.1039/c8sc01353e



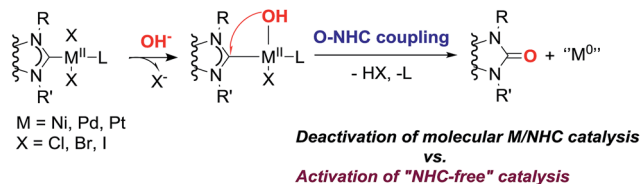

Scheme 1 Discovered O–NHC coupling reactions in M/NHC systems.

explains why the replacement of CsOPiv bases by Bu<sub>3</sub>N switches the reaction toward Michael addition.<sup>7c</sup> Yet another important role of bases, the catalyst activation *via* reduction of M(+)L complexes to active M(0)L molecular complexes, should be considered. In this type of catalyst activation, bases like alcoholates or amines can act as either direct reductants *via* hydride transfer,<sup>4a,9</sup> or promoters of reductive elimination of the "leaving"  $\pi$ -coordinated allyl ligands *via* nucleophilic addition to the allyl  $\pi$ -system.<sup>10</sup>

Within the framework of the current concept, the M/NHC core is thought to confer the catalytic activity, whereas the bases are thought to be responsible for the chemical versatility. Boosts of catalytic performance observed with M/NHC complexes are typically attributed to ligand effects on the chemical transformation studied or optimization of reaction conditions. Recently, the ability of aliphatic amine bases to induce cleavage of M–NHC bonds with the fast release of catalytically active NHC-free metal species has been reported.<sup>11</sup> Decomposition of M/NHC complexes in the presence of strong bases was reported in a few cases.<sup>12</sup> However, activation/deactivation of M/NHC complexes with bases, which would cause transformations of NHC ligands and affect the M–NHC bonds, remain understudied.

In the present work, we reveal a transformation of M/NHC (M = Pd, Pt, Ni) complexes taking place in the presence of most widely applied bases, such as KOH, NaOH, *t*-BuOK, Cs<sub>2</sub>CO<sub>3</sub>, K<sub>2</sub>CO<sub>3</sub>, *etc.* The transformation reported here actually may take

place in a number of already known catalytic systems;<sup>5</sup> however, it was not reported previously.

A new base-mediated reaction of O–NHC coupling is discovered, leading to "NHC-free" metal species and azolones (Scheme 1) under conditions typical for M/NHC catalyzed reactions. By virtue of the O–NHC coupling, NHC ligands act as intrinsic reducing agents to produce M(0) species. "Ligandless" metal species are renowned for their high chemical activity and outstanding catalytic performance. The revealed O–NHC coupling reaction can occupy a dominant place in the whole process by controlling the generation of active centers or initiating deactivation of a catalytic system, depending on particular catalytic mechanisms.


## Results and discussion

### Transformations of M/NHC complexes under the action of bases


A variety of NHC ligands (16 examples) and M/NHC complexes of Pd, Pt, Ni (25 examples) were tested to estimate the scope of the revealed reaction (Scheme 2). A set of typical bases including KOH, NaOH, K<sub>2</sub>CO<sub>3</sub>, Cs<sub>2</sub>CO<sub>3</sub>, *t*-BuOK, and *t*-BuONa were employed in these experiments (Table S1†). Solvents, temperatures and reaction times (40–140 °C, 3–24 h) used here correspond to typical reaction conditions used for a variety of reported catalytic reactions.<sup>1–4,6,7,13</sup>

For all of the bases, decomposition of the metal complexes leading to precipitation of agglomerated M(0) nanoparticles (M = Pd, Pt, Ni) or Ni(OH)<sub>2</sub> was observed. Compositions and structures of the metal precipitates were determined by X-ray fluorescence spectroscopy (XRF), field-emission scanning electron microscopy (FE-SEM, Fig. 1 and ESI†), and Raman spectroscopy.

Reactions of complexes 2–6 with bases can be divided into three different types depending on the main reaction product structures (Scheme 3). Plausible stoichiometry for the reactions is presented in Scheme S2.†

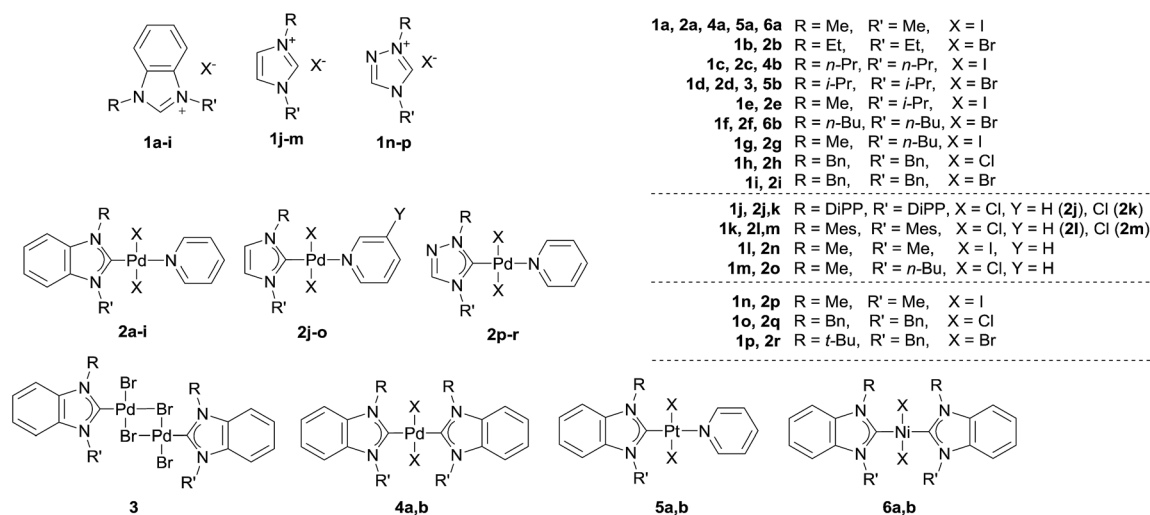

Scheme 2 Overview of the ligand precursors (1) and metal complexes (2–6) utilized in the present study.



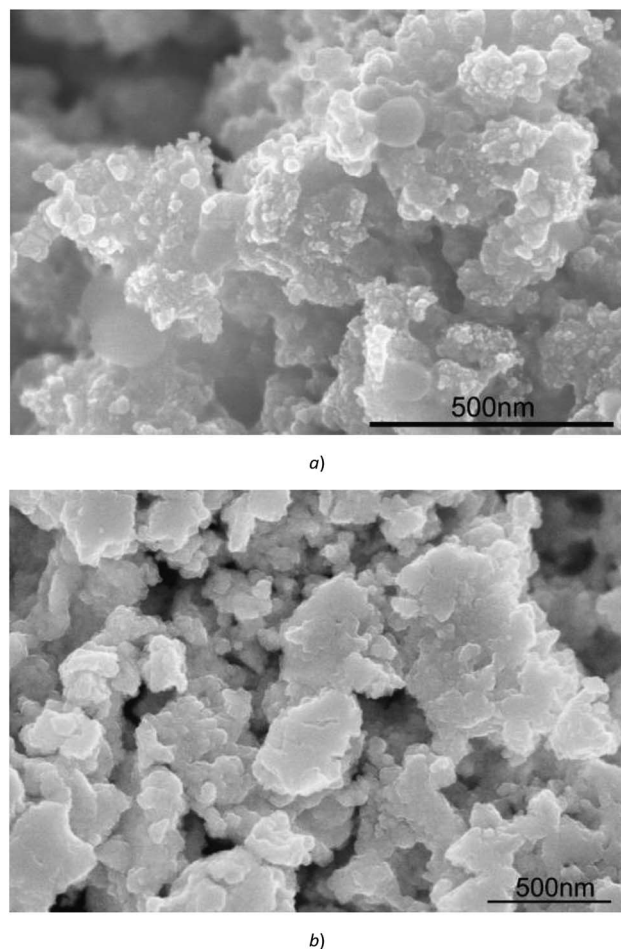


Fig. 1 FE-SEM images of palladium (a) and platinum (b) precipitates isolated from reaction mixtures after heating complex **2a** with KOH in pyridine at 100 °C for 24 h and complex **5a** with *t*-BuOK in 1,4-dioxane at 100 °C for 20 h, respectively.

Type 1 reactions involved palladium complexes **2** and **3** and platinum complexes **5a** and **b** to yield free metal particles of Pd(0) and Pt(0) (Fig. 1) and azolones **7a–o** with all of the bases (Scheme 3, Table S1†).

Type 2 reactions were observed for bis-NHC complexes **4a** and **b** and **6a** and **b**. Heating complexes **4a** and **b** with KOH and *t*-BuOK, and heating complexes **6a** and **b** with *t*-BuOK resulted in formation of Pd(0) and Ni(0) precipitates, correspondingly, and azolones **7a**, **c** and **f** (quantitatively detected as 1 mol per mole of the initial complex) as the main products. However, diamines **8a–c** were also detected by HPLC and GC-MS in the reaction mixtures (Scheme 3, Table S1†).

A Type 3 reaction was observed for nickel complex **6a**, which transformed into Ni(OH)<sub>2</sub> and diamine **8a** when heated with aqueous KOH in dioxane (Scheme 3). Only trace amounts of 1,3-dimethylbenzimidazolone **7a** (yields up to 9%) were detected by HPLC and GC-MS in the reaction mixture.

The main product yields strongly depended on the structure of the initial complex, the base, and the solvent. Comparing the reactivities of the complexes toward *t*-BuOK in Type 1 and Type 2 reactions, it could be concluded that Pd complexes **2** and the

halogen-bridged complex **3** were the most reactive, bis-NHC Pd complexes **4** were significantly less reactive, and Pt complexes **5** and Ni complexes **6** were the least reactive (Table S1†). Notably, the reaction proceeded even at 40 °C and was accelerated upon heating (see variable temperature experiments, Fig. S1†). As an illustration, compound **2a** was converted almost completely within ~20 min when heated with *t*-BuOK in dioxane at 100 °C to give benzimidazolone **7a** in ~80% yield, while it required 3 h for complexes **4a** and **b** to give good yields of azolones **7a** and **c** (86–87%) (Table S1†). Even more, promoting the reaction with Pt complexes **5a** and **b** and Ni complexes **6a** and **b** required heating for ~20 h and ~48 h, respectively.

Concerning the possible influence of the structure of NHC ligands, metal complexes with bulky substituents, especially DiPP and Mes (compounds **2j–m**), reacted somewhat slower. The yields of azolones **7** dramatically depended on the heterocycle type of the NHC ligands. The highest yields of azolones **7** were obtained for complexes **2a–i**, **3**, **4a** and **b**, **5a** and **b**, and **6a** and **b** with NHC ligands of benzimidazole type, which formed stable benzimidazol-2-ones **7a–h**. For complexes **2j–r** comprising NHC ligands of imidazole and 1,2,4-triazole series (except the **2j–m** complexes with bulky substituted *N,N'*-aryl-imidazoles), only trace yields of the corresponding azolones **7k–o** were detected by GC-MS (see ESI†). Low yields of imidazol-2-ones and triazol-5-ones were related to their instability and solvolysis (discussed below in more detail).




By comparing the effects of different bases on **2a–i** Pd complexes it could be noticed that stronger bases like *t*-BuOK, *t*-BuONa, KOH, and NaOH provided higher reaction rates and higher benzimidazol-2-ones yields (43–97%) than mild and less soluble K<sub>2</sub>CO<sub>3</sub> and Cs<sub>2</sub>CO<sub>3</sub> (~0–57%) (Table S1†). Remarkably, Pt complexes **5a** and **b** were almost unreactive toward KOH in dioxane within 20 h, while they afforded 42% and 65% HPLC yields of azolones **7a** and **d** with *t*-BuOK under the same conditions (Table S1†). The Type 3 reaction observed for complex **6a**, heated with aqueous KOH in dioxane, may be considered as a fresh example of Ni-NHC hydrolysis (see a more detailed discussion below).<sup>14</sup>

Yields of azolone **7a** in the reaction between complex **2a** and *t*-BuOK in 2-propanol (62%) and DMF (58%) were lower than those in dioxane (91%) and pyridine (95%) (Table S1†). The lower yields may be explained by concurrent partial reduction of Pd(II)NHC to Pd(0) species and azolium salts/NHC in these solvents.<sup>15</sup> Azolium salts and NHCs subsequently undergo solvolysis to form diaminobenzenes (see discussion below).

### Mechanistic study of azolone formation

Consideration of the results raises a question: what pathways lead from the metal complexes to azolones in the presence of strong oxygen bases? It should be noted that azolium salts **1** heated with KOH and *t*-BuOK under the conditions that favor decomposition of complexes **2–6** produce quite low yields of azolones (≤10%), probably *via* the disproportionation reaction.<sup>16</sup> This result makes it impossible to explain the high yields of azolones **7** by simple solvolysis of complexes **2–6** and subsequent disproportionation of azolium salts.

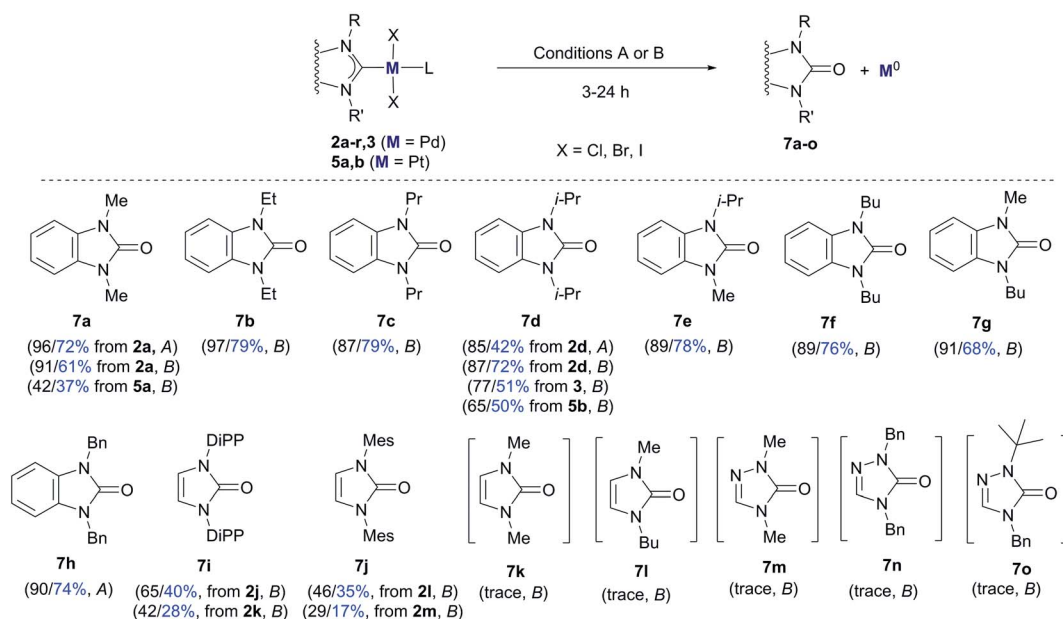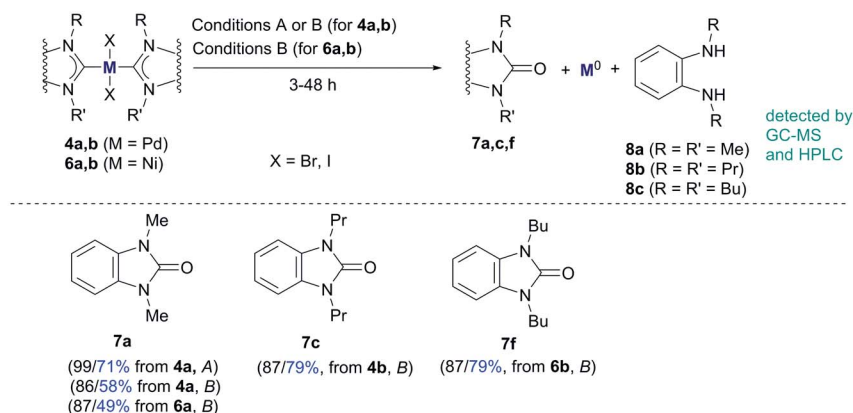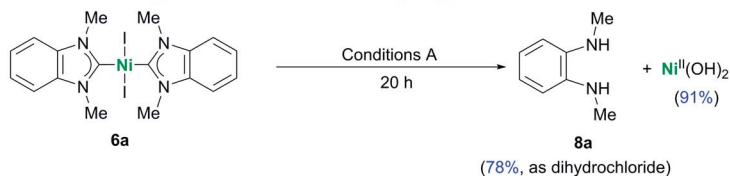

Type 1: Transformation to  $M^{(0)}$  and azolonesType 2: Transformation to  $M^{(0)}$ , azolones and diaminesType 3: Transformation to  $Ni(OH)_2$  and diamines

**Scheme 3** Reactions of  $M/NHC$  complexes with  $KOH$  (Conditions A) and  $t\text{-BuOK}$  (Conditions B). HPLC and isolated (blue color) yields are shown for each case. HPLC/isolated yields are calculated assuming that, theoretically, 1 mole of azolone **7a**, **c**, and **f** is formed from 1 mole of the complex **4a** and **b**, and **6a** and **b**. Conditions A:  $KOH$ ,  $H_2O$ , pyridine,  $100^\circ C$ ; Conditions B:  $t\text{-BuOK}$ , 1,4-dioxane,  $100^\circ C$ . For additional details and other reaction conditions see the Experimental section, Table S1 and Fig. S1†


To evaluate the formation of azolones **7** directly in the reaction of  $M/NHC$  complexes with bases rather than during the isolation procedures or preparation of analytic samples, we performed ESI-MS online monitoring of the reaction for a selection of complexes, **2a**, **b**, **o**, and **r**, and **4a** (Fig. S2–S11†). ESI-MS online monitoring is a powerful method for detecting charged or ionizable reactants, intermediates, and products

directly in the course of metal-catalyzed reactions.<sup>17</sup> A solution of a particular complex in THF was heated at  $100^\circ C$  with continuous transfusing to a mass spectrometer. After  $\sim 1$  min, an aqueous solution of  $KOH$  (or a suspension of  $t\text{-BuOK}$  in THF) was injected into the reaction mixture, initiating almost immediate appearance of the corresponding azolone **7a**, **b**, **l**, or **o** (details in the ESI†). To corroborate that the base was the







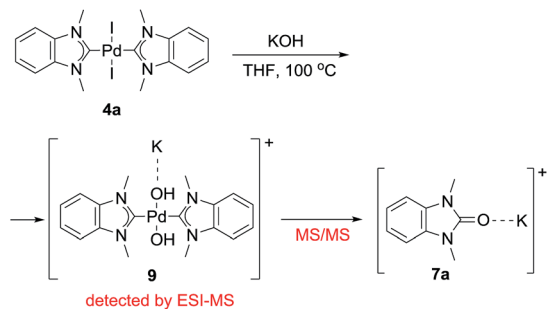

**Scheme 6** Formation of hydroxy-complex **9** and its transformation into azolone **7a** during the reaction of complex **4a** with KOH (ESI-MS online and MS/MS experiments).


explained by a transformation shown in Scheme 7. At the first stage, O–NHC coupling with a base gives an azolone (1 mol per mole of  $M(\text{NHC})_2\text{X}_2$ ) and a NHC (in equilibrium with its protonated form, *i.e.* azolium cation). At the second stage, the released NHC undergoes solvolysis to give diamine **8** under strongly basic conditions *via* the known reaction mechanism (Schemes 7 and S1, and details in the ESI†).<sup>16</sup>

Reaction of nickel complex **6a** with aqueous KOH giving  $\text{Ni}(\text{OH})_2$  and diamine **8a** (Scheme 8) could be predicted from previously published data on facile hydrolysis of Ni/NHC complexes producing azolium salts and  $\text{Ni}(\text{OH})_2$  in the presence of water.<sup>14</sup> Benzimidazolium salt **1a**, the intermediate product of the reaction, undergoes solvolysis to diamine **8a**.<sup>16</sup> The solvolysis is accompanied by the formation of small amounts (~9% HPLC yield) of azolone **7a** *via* the parallel disproportionation mechanism (Scheme S1 and discussion in the ESI†).<sup>16</sup>


To check the proposed schemes of the formation of diamines **8** from benzimidazolium salts, a model reaction of azolium salts **1a**, **c**, and **f** with *t*-BuOK in 1,4-dioxane was examined. Diamines **8a–c** (82–85% HPLC yields) and azolones **7a**, **c**, and **f** (8–10% HPLC yields) were the major products, in full compliance with the proposed schemes.

### Possible impacts of the revealed base effect on catalytic reactions

The three different reactions chosen to investigate the impact of the revealed O–NHC coupling on catalytic performance were: the Mizoroki–Heck reaction (1), the Suzuki–Miyaura cross-coupling (2), and C–H functionalization (3) as shown in

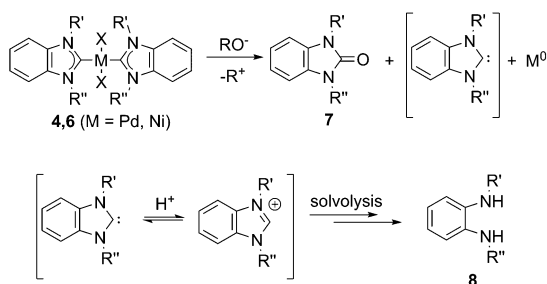

**Scheme 7** Formation of diamines **8** from complexes **4** and **6**.

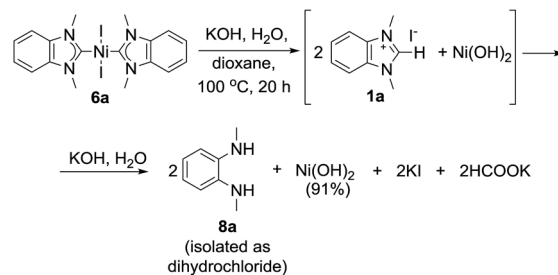


**Scheme 8** Reaction of complex **6a** with KOH.

Scheme 9. Pd/NHC complex **2j** which is frequently used in catalysis was selected as a precatalyst for the reactions (1)–(3).

The reactions (1)–(3) were performed in two distinct manners, methods A and B (Scheme 9). In the method A, freshly prepared solution of the complex **2j** in pyridine was used as the catalyst. In the method B, the precatalyst **2j** was heated with *t*-BuOK in pyridine, neutralized by pyridine hydrochloride, and the solution obtained was introduced to the reaction mixtures (see the Experimental part for details). It is important to note that decomposition of the complex **2j** to give azolone **7i** in the course of the pretreatment (method B) was confirmed by GC–MS. The obtained experimental data are shown in Scheme 9.

In the Mizoroki–Heck reaction (1) performed without initial pre-activation (method A), complex **2j** was almost inactive, only a minor yield of the product **12** was observed. However, in the experiment with the *t*-BuOK pretreatment (method B), the catalytic activity of the precatalyst solution was significantly higher. Thus, in the Mizoroki–Heck reaction (1), O–NHC coupling leads to activation of the Pd/NHC catalyst, apparently

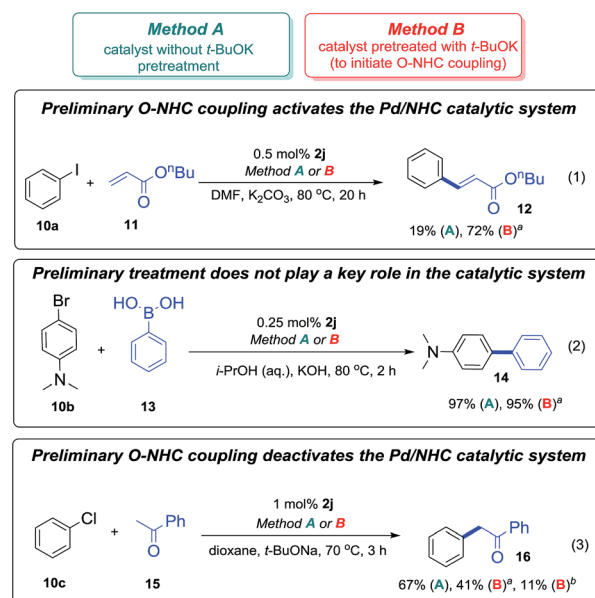

**Scheme 9** Possible impacts of O–NHC coupling on Pd-catalyzed C–C coupling reactions. (a) Pretreatment of the catalyst with *t*-BuOK for 10 min at 100 °C. (b) Pretreatment of the catalyst with *t*-BuOK for 3 h at 100 °C.



by promoting the formation of “NHC-free” Pd active species. High performances in cocktail-type systems is a distinctive feature of the Mizoroki–Heck reaction.<sup>18c,20</sup> Removal of the NHC ligands favours generation of a cocktail-type system and facilitates the product formation.

In the Suzuki–Miyaura reaction (2), formation of product **14** was observed in both cases. Since transmetallation usually represents a rate-limiting step of this cross-coupling reaction, M/NHC catalytic species and ligand-free cocktail-type systems may show similar performances. Although it affects the formation of “NHC-free” metal species in solution, O–NHC coupling has no determining effect on the outcomes of the Suzuki–Miyaura reaction.

In the C–H arylation reaction (3) carried out in the presence of *t*-BuOK, only a fresh solution of the complex **2j** was fairly active (Scheme 9). The catalytic solution obtained after the *t*-BuOK pretreatment (method B) was less active, and its activity significantly decreased with prolongation of the pretreatment time from 10 min to 3 h. Formation of azolone **7i** due to slow decomposition of **2j** in the course of the reaction (method A) was also detected by GC–MS. Thus, in the C–H functionalization reaction (3) O–NHC coupling causes deactivation of Pd/NHC catalytic systems. The results suggest that Pd/NHC are catalytically active species, while ligand-free or cocktail-type systems are less efficient or inactive.

The results outlined in Scheme 9 clearly corroborate the importance of the base-mediated O–NHC coupling for the catalytic activity of M/NHC complexes. Base-mediated M–NHC bond cleavage revealed in the current study can largely determine the behavior of catalytically active metal species.

On the one hand, the O–NHC coupling reaction can provoke decomposition of M/NHC complexes and thus accelerate deactivation of catalytic systems where only molecular M/NHC complexes are capable of driving the catalytic cycle (classical homogeneous molecular M/NHC catalysis). In such systems, when strong bases like alkali metal alkoxides or hydroxides are applied, O–NHC coupling can represent a serious problem that needs to be solved for providing stability and high performance of the catalytic systems.

On the other hand, the opposite effect of the O–NHC coupling may be anticipated in reactions where M/NHC complexes serve as a source of “NHC-free” active metal species without typical metal–NHC bonds. As an example, the activity of Pd/NHC systems in the Mizoroki–Heck reaction is determined predominantly by the cleavage of the metal–NHC bond and generation of cocktail-type catalytic systems, in which the “NHC-free” palladium species act as truly active catalytic centers.<sup>18c</sup> The proposed pathways leading from M/NHC complexes to the cocktails of active metal species include transformation of the NHC ligands *via* C–H or C–C coupling and formation of corresponding azolium salts. The plausible role of aliphatic amine bases as hydride sources and reductants of metal cations in M/NHC complexes to produce azolium salts and “NHC-free” active metal species *via* H–NHC (C–H) coupling was reported recently.<sup>11</sup> As described here, a principally new mechanism for generation of the “NHC-free” active species can be implemented in the presence of oxygen bases like KOH, *t*-

BuOK, or alkali metal carbonates. In such systems, NHC ligands play a role in the reduction of M(II) to M(0) by means of the O–NHC coupling reaction affording “NHC-free” M(0) active species and azolones.

## Conclusions

Complexes of metals with N-heterocyclic carbenes, M(NHC)<sub>X</sub><sub>2</sub>L [M = Pd(II), Pt(II), Ni(II)], react with oxygen bases typically applied in various catalytic processes to give M(0) nanoparticles and azol-2(5)-ones. In this previously undescribed O–NHC coupling reaction, NHC ligands play the role of two-electron intramolecular reductants of the coordinated metal dications. The base anions serve as a source of oxygen. The azol-2(5)-ones forming from the NHC of imidazole and 1,2,4-triazole series are labile compounds that decompose with the destruction of heterocycles.

Among Pd(II), Pt(II), and Ni(II) complexes examined in this work, Pd complexes are found to be the most reactive and thus more prone to the O–NHC coupling. A combination of Pd with NHC ligands gives a flexible catalytic system, whose nature can be tuned from the Pd/NHC to “NHC-free” molecular or cluster/nanoparticle catalysis.

The base-mediated O–NHC coupling has a significant impact on the performance of the M/NHC catalytic systems. On one hand, the reaction provokes deactivation of these catalytic systems, where participation of molecular M/NHC complexes in the transition state of a catalytic reaction is essential, like in the chiral NHC–metal-based asymmetric catalysis. Certainly, O–NHC coupling should be a problem for homogeneous M/NHC catalysis when highly active palladium complexes and strong bases like alkali metal alcoholates or hydroxides are applied. The present study clearly demonstrates that the suppression of O–NHC coupling is an important, overlooked priority in maintaining the high efficiency of well-defined M/NHC systems in the catalysis of numerous reactions mediated by strong oxygen bases.

On the other hand, the base-mediated O–NHC coupling can serve as a driving force in the activation of M/NHC systems for the reactions catalyzed by “NHC-free” metal species. The latter scheme is valid, for example, for the high-temperature Mizoroki–Heck reaction.

Indeed, the correct choice of base is essential for maximizing the performance of the M/NHC catalytic systems and we anticipate many studies in this regard in the nearest future.

## Experimental section

### General information

<sup>1</sup>H and <sup>13</sup>C{<sup>1</sup>H} NMR spectra were acquired on a Bruker DRX 500 instrument at 500 MHz and 125 MHz, respectively, in DMSO-*d*<sub>6</sub> or CDCl<sub>3</sub>. <sup>1</sup>H and <sup>13</sup>C{<sup>1</sup>H} chemical shifts are given in ppm relative to the residual peak of the solvent ( $\delta$  2.5 for DMSO and 7.26 for CHCl<sub>3</sub>) for the proton spectra and the <sup>13</sup>C{<sup>1</sup>H} DMSO-*d*<sub>6</sub> signal ( $\delta$  39.5) or the CDCl<sub>3</sub> signal ( $\delta$  77.2) for the carbon spectra.



High-resolution mass spectra were obtained on a Bruker maXis Q-TOF or microTOF instruments (Bruker Daltonik GmbH, Bremen, Germany) equipped with an electrospray ionization (ESI) ion source. The experiments were performed in positive (+) MS ion mode (HV Capillary: 4500 V; Spray Shield Offset: −500 V) with a scan range of  $m/z$  50–1500. External calibration of the mass spectrometer was achieved using a low-concentration tuning mix solution (Agilent Technologies). Unless otherwise stated, direct syringe injection was applied for the analyzed solutions in MeCN (flow rate:  $3 \mu\text{L} \times \text{min}^{-1}$ ). Nitrogen was applied as the nebulizer gas (0.4 bar) and dry gas ( $4.0 \text{ L} \times \text{min}^{-1}$ ,  $180^\circ\text{C}$ ). All the MS spectra were recorded with 1 Hz frequency and processed using Bruker Data Analysis 4.0 software.

HPLC analyses were accomplished using an Agilent 1260 Infinity LC system equipped with a reversed-phase Zorbax SB-C18 column ( $50 \times 4.6 \text{ mm}$ ) thermostated at  $35^\circ\text{C}$  and a detection wavelength of 280 nm. Gradient elution with a  $1 \text{ mL min}^{-1}$  flow rate was applied. The mobile phase A consisted of 10% MeCN aqueous solution, the phase B was neat MeCN, and the phase C was 0.02 M  $\text{NaClO}_4$  aqueous solution. The following gradient conditions were used: ramp over 3 min from 80% A and 20% C to 80% B and 20% C; then hold 5 min.

GC-MS experiments were carried out with an Agilent 7890A GC system, equipped with an Agilent 5975C mass-selective detector (electron impact, 70 eV) and a HP-5MS column ( $30 \text{ m} \times 0.25 \text{ mm} \times 0.25 \mu\text{m}$  film) using He as carrier gas at a flow of  $1.0 \text{ mL min}^{-1}$ .

For electron microscopy measurements, the samples were mounted on a 25 mm aluminum specimen stub, fixed by conductive carbon tape and coated with a thin film (15 nm) of carbon. The observations were carried out using a Hitachi SU8000 field-emission scanning electron microscope (FE-SEM). Images were acquired in secondary electron mode at 10 kV accelerating voltage and at a working distance of 4–5 mm. The morphology of the samples was studied taking into account the possible influence of the carbon coating on the surface. EDS-SEM studies were carried out using an Oxford Instruments X-max 80 EDS system at 10 kV accelerating voltage and at a working distance of 15 mm.

Raman spectra were recorded using an InVia Raman microscope (Renishaw, UK) equipped with a 20 mW 514.5 nm argon laser. All the spectra were collected using a  $50\times$  objective lens, 20 s of acquisition time, and 3 accumulations. A silicon wafer was used for calibration.<sup>21</sup>

C, H, and N elemental analyses were performed using a PerkinElmer 2400 elemental analyzer. Melting points were determined in open capillary tubes using a Thiele apparatus and are uncorrected. The Ni, Pd, and Pt contents in metal precipitates were determined by means of energy dispersive X-ray fluorescence spectroscopy (ARL Quant'X EDXRF Analyzer, Thermo Scientific). For the analyses, the weighed samples of metal precipitates were dissolved in aqueous aqua regia.

Experiments concerning reactions of M/NHC complexes with bases were performed under an argon atmosphere using standard Schlenk techniques. Solvents were dried over activated 3 Å molecular sieves and degassed by argon bubbling within 20 min. Preparative column chromatography was performed using silica gel 60 (230–400 mesh, Merck).

1-Methylbenzimidazole,<sup>22</sup> 1,3-dimethyl-1*H*-benzimidazol-3-ium iodide (**1a**),<sup>23</sup> 1,3-diethyl-1*H*-benzimidazol-3-ium bromide (**1b**),<sup>24</sup> 1,3-di-*n*-propyl-1*H*-benzimidazol-3-ium iodide (**1c**),<sup>11</sup> 1,3-di(propan-2-yl)-1*H*-benzimidazol-3-ium bromide (**1d**),<sup>25</sup> 1,3-dibutyl-1*H*-benzimidazol-3-ium bromide (**1f**),<sup>14</sup> 1-butyl-3-methyl-1*H*-benzimidazol-3-ium iodide (**1g**),<sup>14</sup> 1,3-dibenzyl-1*H*-benzimidazol-3-ium chloride (**1h**),<sup>18c</sup> 1,3-dibenzyl-1*H*-benzimidazol-3-ium bromide (**1i**),<sup>18c</sup> 1,3-bis[2,6-di(propan-2-yl)phenyl]-1*H*-imidazol-3-ium chloride (**1j**),<sup>14</sup> 1,3-bis(2,4,6-trimethylphenyl)-1*H*-imidazol-3-ium chloride (**1k**),<sup>14</sup> 1,3-dimethyl-1*H*-imidazol-3-ium iodide (**1l**),<sup>14</sup> 1,4-dimethyl-4*H*-1,2,4-triazol-1-ium iodide (**1n**),<sup>14</sup> 1,4-dibenzyl-4*H*-1,2,4-triazol-1-ium chloride (**1o**),<sup>18c</sup> 4-benzyl-1-*tert*-butyl-4*H*-1,2,4-triazol-1-ium bromide (**1p**),<sup>14</sup> (1,3-dimethyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)diiodo(pyridine)palladium (**2a**),<sup>18c</sup> (1,3-dipropyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)(diiodo)(pyridine)palladium (**2c**),<sup>11</sup> dibromo[1,3-di(propan-2-yl)-1,3-dihydro-2*H*-benzimidazol-2-ylidene](pyridine)palladium (**2d**),<sup>26</sup> dibromo(1,3-dibutyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)(pyridine)palladium (**2f**),<sup>18c</sup> dichloro(1,3-dibenzyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)(pyridine)palladium (**2h**),<sup>18c</sup> dibromo(1,3-dibenzyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)(pyridine)palladium (**2i**),<sup>18c</sup> {1,3-bis[2,6-di(propan-2-yl)phenyl]-1,3-dihydro-2*H*-imidazol-2-ylidene}dichloro(pyridine)palladium (**2j**),<sup>27</sup> {1,3-bis[2,6-di(propan-2-yl)phenyl]-1,3-dihydro-2*H*-imidazol-2-ylidene}(dichloro)(3-chloropyridine)palladium (**2k**),<sup>28</sup> [1,3-bis(2,4,6-trimethylphenyl)-1,3-dihydro-2*H*-imidazol-2-ylidene](dichloro)(pyridine)palladium (**2l**),<sup>28</sup> [1,3-bis(2,4,6-trimethylphenyl)-1,3-dihydro-2*H*-imidazol-2-ylidene](dichloro)(3-chloropyridine)palladium (**2m**),<sup>28</sup> (1,3-dimethyl-1,3-dihydro-2*H*-imidazol-2-ylidene)diiodo(pyridine)palladium (**2n**),<sup>18c</sup> dichloro(1-butyl-3-methyl-1,3-dihydro-2*H*-imidazol-2-ylidene)(pyridine)palladium (**2o**),<sup>18c</sup> (2,4-dimethyl-2,4-dihydro-3*H*-1,2,4-triazol-3-ylidene)diiodo(pyridine)palladium (**2p**),<sup>18c</sup> dichloro(2,4-dibenzyl-2,4-dihydro-3*H*-1,2,4-triazol-3-ylidene)(pyridine)palladium (**2q**),<sup>18c</sup> (4-benzyl-2-*tert*-butyl-2,4-dihydro-3*H*-1,2,4-triazol-3-ylidene)dibromo(pyridine)palladium (**2r**),<sup>18c</sup> di- $\mu$ -bromo(dibromo)bis[1,3-di(propan-2-yl)-1,3-dihydro-2*H*-benzimidazol-2-ylidene]dipalladium (**3**),<sup>25</sup> bis(1,3-dimethyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)diiodopalladium (**4a**),<sup>29</sup> bis(1,3-dipropyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)(di-iodo)palladium (**4b**),<sup>11</sup> (1,3-dimethyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)diiodo(pyridine)platinum (**5a**),<sup>30</sup> dibromo[1,3-di(propan-2-yl)-1,3-dihydro-2*H*-benzimidazol-2-ylidene](pyridine)platinum (**5b**),<sup>31</sup> bis(1,3-dimethyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)diiodonickel (**6a**),<sup>32</sup> dibromo[bis(1,3-dibutyl-1,3-dihydro-2*H*-benzimidazol-2-ylidene)]nickel (**6b**),<sup>14</sup> 1-butyl-3-methyl-1,3-dihydro-2*H*-imidazol-2-one (**7l**),<sup>33</sup> and 2,4-dibenzyl-2,4-dihydro-3*H*-1,2,4-triazol-3-one (**7n**)<sup>34</sup> were synthesized as described in the literature. All other chemicals were commercially available.

### 1-Methyl-3-(propan-2-yl)-1*H*-benzimidazol-3-ium iodide (**1e**)

A mixture of 1-methylbenzimidazole (1.3 g, 0.01 mol), isopropyl iodide (3.4 g, 0.02 mol) and acetonitrile (15 mL) was heated under reflux for 24 h. Then the reaction mixture was evaporated to dryness *in vacuo*. The residue obtained was recrystallized from the MeCN–acetone 1 : 2 mixture, washed with acetone and





dried *in vacuo*. Yield 2.69 g (89%) of colorless crystals, mp 195–198 °C.  $^1\text{H}$  NMR ( $\text{DMSO}-d_6$ ):  $\delta$  1.62–1.63 (m, 6H,  $2\text{CH}_3$ ), 4.09 (s, 3H,  $\text{CH}_3$ ), 5.04–5.12 (m, 1H, CH), 7.67–7.71 (m, 2H, Ar), 8.02–8.05 (m, 1H, Ar), 8.13–8.15 (m, 1H, Ar), 9.89 (s, 1H, H-2).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{DMSO}-d_6$ ):  $\delta$  21.6, 33.4, 50.3, 113.5, 113.7, 126.26, 126.34, 130.2, 131.9, 141.1. ESI-MS(TOF) calcd for  $\text{C}_{11}\text{H}_{15}\text{N}_2$   $[\text{M} - \text{I}]^+$   $m/z$  175.1230, found  $m/z$  175.1227.

### General procedure for the preparation of compounds 2b, e, and g

A stirred mixture of corresponding azolium salts **1b**, **e**, and **g** (1.05 mmol), KBr or KI (5 mmol), anhydrous  $\text{K}_2\text{CO}_3$  (690 mg, 5 mmol),  $\text{PdCl}_2$  (177 mg, 1 mmol) and dry pyridine (8 mL) was heated for 16 h at 80 °C in a sealed glass vial. After cooling to 20 °C, the reaction mixture was diluted with  $\text{CH}_2\text{Cl}_2$  (20 mL) and passed through a short pad of silica gel eluting with  $\text{CH}_2\text{Cl}_2$  until the yellow product was completely recovered. The obtained solution was evaporated to dryness under vacuum (rotary evaporator) at 40 °C. The residue obtained was treated with hexane (~10 mL). The precipitate formed was collected by filtration and recrystallized from the  $\text{CH}_2\text{Cl}_2$ –hexan 1 : 3 mixture.

**Dibromo(1,3-diethyl-1,3-dihydro-2H-benzimidazol-2-ylidene)-(pyridine)palladium (2b).** Yield 395 mg (76%), yellow prismatic crystals.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.72 (t,  $J = 7.3$  Hz, 6H,  $2\text{CH}_3$ ), 4.93 (q,  $J = 7.3$  Hz, 4H,  $2\text{CH}_2$ ), 7.28–7.30 (m, 2H, Ar), 7.36–7.42 (m, 4H, Ar), 7.77–7.80 (m, 1H, Ar), 9.10–9.11 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  14.5, 44.0, 110.5, 123.1, 124.7, 134.4, 138.1, 152.8, 161.1. Anal. calcd for  $\text{C}_{16}\text{H}_{19}\text{Br}_2\text{N}_3\text{Pd}$ : C, 36.99; H, 3.69; N, 8.09. Found: C, 37.15; H, 3.61; N, 7.89.

**Diiodo[1-methyl-3-(propan-2-yl)-1,3-dihydro-2H-benzimidazol-2-ylidene](pyridine)palladium (2e).** Yield 454 mg (74%), yellow prismatic crystals.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.78 (d,  $J = 7.3$  Hz, 6H,  $2\text{CH}_3$ ), 4.17 (s, 3H,  $\text{CH}_3$ ), 6.00–6.08 (m, 1H, CH), 7.22–7.28 (m, 2H, Ar), 7.34–7.37 (m, 3H, Ar), 7.55–7.56 (m, 1H, Ar), 7.75–7.78 (m, 1H, Ar), 9.11–9.12 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  20.2, 35.7, 54.8, 110.3, 112.4, 122.6, 122.8, 124.7, 132.6, 136.6, 137.9, 154.1, 159.1. Anal. calcd for  $\text{C}_{16}\text{H}_{19}\text{I}_2\text{N}_3\text{Pd}$ : C, 31.32; H, 3.12; N, 6.85. Found: C, 31.45; H, 3.19; N, 6.71.

**(1-Butyl-3-methyl-1,3-dihydro-2H-benzimidazol-2-ylidene)-(diiodo)(pyridine)palladium (2g).** Yield 509 mg (81%), yellow prismatic crystals.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.09 (t,  $J = 7.4$  Hz, 3H,  $\text{CH}_3$ ), 1.54–1.61 (m, 2H,  $\text{CH}_2$ ), 2.19–2.25 (m, 2H,  $\text{CH}_2$ ), 4.19 (s, 3H,  $\text{CH}_3$ ), 4.69–4.72 (m, 2H,  $\text{NCH}_2$ ), 7.25–7.28 (m, 2H, Ar), 7.34–7.37 (m, 4H, Ar), 7.74–7.77 (m, 1H, Ar), 9.07–9.08 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  13.9, 20.5, 30.6, 36.1, 49.2, 110.0, 110.4, 122.89, 122.92, 124.7, 134.8, 135.5, 137.9, 154.0, 160.5. Anal. calcd for  $\text{C}_{17}\text{H}_{21}\text{I}_2\text{N}_3\text{Pd}$ : C, 32.53; H, 3.37; N, 6.70. Found: C, 32.38; H, 3.29; N, 6.83.

### General procedure for the reaction of complexes 2–6 with KOH or *t*-BuOK

**Method A.** A mixture of the complex **2a**, **d**, **h**, and **i**, and **4a** (0.3 mmol), pyridine (4 mL) and 3 M aqueous KOH solution (1 mL, 3 mmol) was vigorously stirred in a Teflon screw cap tube at 100 °C within 3–24 h (Table S1<sup>†</sup>), then cooled to 20 °C and

neutralized with HCl solution to pH 8–9 under an argon atmosphere. The resulted mixture was centrifuged and analyzed by HPLC and GC-MS. A precipitate separated by centrifugation was washed sequentially with MeCN ( $3 \times 4$  mL), DMF (3 mL) water ( $3 \times 4$  mL), and acetone ( $3 \times 4$  mL), and then dried *in vacuo* to give corresponding metal powder, Pd(0) or Pt(0). The organic solution formed after centrifugation was combined with washings and evaporated to dryness *in vacuo*. The residue obtained was dissolved in  $\text{CHCl}_3$  (10 mL), washed with saturated aqueous solution of NaCl ( $3 \times 2$  mL), dried with anhydrous  $\text{Na}_2\text{SO}_4$  and evaporated to a small volume (~2 mL). The corresponding azolones were isolated by flash chromatography on silica gel. The yields of azolones are presented in Scheme 3, Table S1.<sup>†</sup>

**Method B.** A mixture of the complex **2–6** (0.3 mmol), 1,4-dioxane (5 mL) and *t*-BuOK (336 mg, 3 mmol) was vigorously stirred in a Teflon screw cap tube at 100 °C within 3–48 h (Table S1<sup>†</sup>), then neutralized with HCl solution to pH ~8 under an argon atmosphere and treated as described in the method A. The yields of azolones are presented in Scheme 3, Table S1.<sup>†</sup>

For the reactions of complexes **2–6** with bases under other conditions, see Table S1 in the ESI.<sup>†</sup>

**1,3-Dimethyl-1,3-dihydro-2H-benzimidazol-2-one (7a).** Colorless needles, mp 104–106 °C (from heptane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  3.42 (s, 6H,  $2\text{CH}_3$ ), 6.95–6.98 (m, 2H, Ar), 7.08–7.11 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  27.3, 107.4, 121.3, 130.2, 154.8. ESI-MS(TOF) calcd for  $\text{C}_9\text{H}_{11}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  163.0866, found  $m/z$  163.0868. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>16</sup>

**1,3-Diethyl-1,3-dihydro-2H-benzimidazol-2-one (7b).** White solid, mp 53–57 °C (from hexane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.34 (t,  $J = 7.2$  Hz, 6H,  $2\text{CH}_3$ ), 3.95 (q,  $J = 7.2$  Hz, 4H,  $2\text{CH}_2$ ), 6.99–7.03 (m, 2H, Ar), 7.07–7.10 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  13.8, 36.0, 107.6, 121.0, 129.3, 153.8. ESI-MS(TOF) calcd for  $\text{C}_{11}\text{H}_{15}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  191.1179, found  $m/z$  191.1176. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>35</sup>

**1,3-Dipropyl-1,3-dihydro-2H-benzimidazol-2-one (7c).** Colorless oil.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  0.97 (t,  $J = 7.4$  Hz, 6H,  $2\text{CH}_3$ ), 1.74–1.83 (m, 4H,  $2\text{CH}_2$ ), 3.85 (t,  $J = 7.3$  Hz, 4H,  $2\text{NCH}_2$ ), 6.96–7.02 (m, 2H, Ar), 7.04–7.10 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  11.5, 21.9, 42.8, 107.7, 120.9, 129.7, 154.5. ESI-MS(TOF) calcd for  $\text{C}_{13}\text{H}_{19}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  219.1492, found  $m/z$  219.1488. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>36</sup>

**1,3-Di(propan-2-yl)-1,3-dihydro-2H-benzimidazol-2-one (7d).** Colorless prisms, mp 72–75 °C (from hexane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.53 (d,  $J = 7.0$  Hz, 12H,  $4\text{CH}_3$ ), 4.75 (sept,  $J = 7.1$  Hz, 2H,  $2\text{CH}$ ), 7.03–7.06 (m, 2H, Ar), 7.14–7.16 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  20.4, 45.0, 109.1, 120.4, 128.6, 153.2. ESI-MS(TOF) calcd for  $\text{C}_{13}\text{H}_{19}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  219.1492, found  $m/z$  219.1495. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>37</sup>

**1-Methyl-3-(propan-2-yl)-1,3-dihydro-2H-benzimidazol-2-one (7e).** Yellowish crystals, mp 51–54 °C (from hexane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.53 (d,  $J = 7.0$  Hz, 6H,  $2\text{CH}_3$ ), 3.40 (s, 3H,  $\text{CH}_3$ ), 4.69–



4.79 (m, 1H, CH), 6.96–7.00 (m, 1H, Ar), 7.04–7.11 (m, 2H, Ar), 7.11–7.15 (m, 1H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  20.4, 27.1, 45.1, 107.5, 109.0, 120.8, 121.0, 128.3, 130.4, 154.0. ESI-MS(TOF) calcd for  $\text{C}_{11}\text{H}_{15}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  191.1179, found  $m/z$  191.1183. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>38</sup>

**1,3-Dibutyl-1,3-dihydro-2H-benzimidazol-2-one (7f).** A yellowish oil.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  0.95 (t,  $J$  = 7.4 Hz, 6H,  $2\text{CH}_3$ ), 1.35–1.43 (m, 4H,  $2\text{CH}_2$ ), 1.71–1.75 (m, 4H,  $2\text{CH}_2$ ), 3.88 (t,  $J$  = 7.3 Hz, 4H,  $2\text{CH}_2$ ), 6.98–7.01 (m, 2H, Ar), 7.05–7.09 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  13.9, 20.2, 30.6, 41.0, 107.7, 120.9, 129.7, 154.4. ESI-MS(TOF) calcd for  $\text{C}_{15}\text{H}_{23}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  247.1805, found  $m/z$  247.1810. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>35,39</sup>

**1-Butyl-3-methyl-1,3-dihydro-2H-benzimidazol-2-one (7g).** Colorless oil.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  0.95 (t,  $J$  = 7.4 Hz, 3H,  $\text{CH}_3$ ), 1.37–1.42 (m, 2H,  $\text{CH}_2$ ), 1.71–1.74 (m, 2H,  $\text{CH}_2$ ), 3.42 (s, 3H,  $\text{CH}_3$ ), 3.88 (t,  $J$  = 7.3 Hz, 2H,  $\text{CH}_2$ ), 6.95–7.01 (m, 2H, Ar), 7.07–7.10 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  13.9, 20.2, 27.2, 30.7, 41.1, 107.5, 107.7, 121.1, 121.2, 129.6, 130.2, 154.6. ESI-MS(TOF) calcd for  $\text{C}_{12}\text{H}_{17}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  205.1335, found  $m/z$  205.1332. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>35</sup>

**1,3-Dibenzyl-1,3-dihydro-2H-benzimidazol-2-one (7h).** Colorless prisms, mp 106–109 °C (from hexane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  5.13 (s, 4H,  $2\text{CH}_2$ ), 6.87–6.89 (m, 2H, Ar), 6.96–6.99 (m, 2H, Ar), 7.27–7.29 (m, 2H, Ar), 7.31–7.36 (m, 8H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  45.2, 108.5, 121.5, 127.6, 127.8, 128.9, 129.5, 136.5, 154.7. ESI-MS(TOF) calcd for  $\text{C}_{21}\text{H}_{19}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  315.1492, found  $m/z$  315.1496. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>40</sup>

**1,3-Bis[2,6-di(propan-2-yl)phenyl]-1,3-dihydro-2H-imidazol-2-one (7i).** White solid (from hexane).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.24 (d,  $J$  = 6.9 Hz, 12H,  $4\text{CH}_3$ ), 1.27 (d,  $J$  = 7.0 Hz, 12H,  $4\text{CH}_3$ ), 2.95–3.00 (m, 4H,  $4\text{CH}$ ), 6.40 (s, 2H,  $2\text{CH}$  of imidazole), 7.26–7.28 (m, 4H, Ar), 7.39–7.42 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  23.8, 24.0, 29.0, 113.3, 124.0, 129.6, 132.4, 147.5, 152.3. ESI-MS(TOF) calcd for  $\text{C}_{27}\text{H}_{37}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  405.2900, found  $m/z$  405.2899. The physical and spectral characteristics of the product obtained are identical to those described in the literature.<sup>41</sup>

**1,3-Bis(2,4,6-trimethylphenyl)-1,3-dihydro-2H-imidazol-2-one (7j).** White solid, mp 186–188 °C (from MeCN–water 1/2).  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  2.20 (s, 12H,  $4\text{CH}_3$ ), 2.31 (s, 6H,  $2\text{CH}_3$ ), 6.32 (s, 2H,  $2\text{CH}$  of imidazole), 6.96 (s, 4H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  18.1, 21.2, 112.4, 129.2, 132.4, 136.5, 138.5, 150.7. ESI-MS(TOF) calcd for  $\text{C}_{21}\text{H}_{25}\text{N}_2\text{O}$   $[\text{M} + \text{H}]^+$   $m/z$  321.1961, found  $m/z$  321.1963. The spectral characteristics of the product obtained are identical to those described in the literature.<sup>41</sup>

### Online ESI-MS monitoring of the O–NHC coupling reaction

Online monitoring of ions in the reaction progress was performed as follows.

A 10 mL Schlenk tube equipped with a magnetic stir bar was thoroughly flushed with Ar. Then degassed THF (4 mL) and

a  $3.07 \times 10^{-3}$  M solution (freeze–pump–thaw degassed) of the corresponding Pd/NHC complexes **2a**, **b**, **o**, and **r**, and **4a** (100  $\mu\text{L}$ ) in THF were charged into the tube under an argon backflush, and the tube neck was closed with a septum. A red PEEK capillary (72 cm) was pulled into the tube through the septum and immersed into the reaction mixture. The tube was placed in a hot glycerol bath. Then, the tube was heated at 100 °C under continuous magnetic stirring. After heating for  $\sim 1$  min, a degassed  $3.57 \times 10^{-1}$  M solution of the corresponding base (100  $\mu\text{L}$ ) was injected into the flask *via* a syringe through the septum. For KOH, solutions in  $\text{H}_2\text{O}$  or  $\text{H}_2^{18}\text{O}$  were used. For *t*-BuOK, a THF suspension was applied. The reaction was monitored until the entire solution volume was transfused into the mass spectrometer. Azolones were monitored as signals of  $[\text{M} + \text{K}]^+$  ions.

**MS/MS experiments.** During the monitoring of the reaction between **4a** and KOH, a specified ion corresponding to the hydroxyl-complex **9** was studied according to the following procedure. Nitrogen was used as a collision gas. The isolated mass parameter corresponding to the center of the desired  $m/z$  interval was set to the nearest tenth ( $m/z$  471.0). The collision energy applied was 15 eV. In-Source Collision Induced Dissociation (ISCID) energy, which refers to the  $\text{MS}^3$  mode, was set to 0 eV. To define the number of time-of-flight events, the acquisition factor was 2 to get a good-quality spectrum.

**1,3-Dimethyl-1,3-dihydro-2H-benzimidazol-2-one- $^{18}\text{O}$  (7a- $^{18}\text{O}$ ).** A two-necked 30 mL glass flask equipped with a magnetic stirring bar was thoroughly flushed with argon streamed *via* a syringe needle pinned into one flask neck through a rubber cork. Then metallic potassium (117 mg, 3 mmol) and degassed dry pyridine (1 mL) were charged into the flask *via* the second neck under an argon backflush. Then the neck was closed with a septum pierced with a syringe needle attached to a calcium chloride tube for the gas outlet. The flask was placed into an ice-water bath. A degassed solution of  $\text{H}_2^{18}\text{O}$  (100 mg, 5 mmol) in dry pyridine (1 mL) was added dropwise *via* a syringe through the septum under vigorous stirring and argon purging. Then a solution of  $\text{H}_2^{18}\text{O}$  (0.9 mL) in pyridine (1 mL) was injected into the flask *via* a syringe through the septum. After vigorous stirring for 10 min, the flask was purged with argon and a solution of the complex **2a** (176 mg, 0.3 mmol) in pyridine (2 mL) was injected into the flask *via* a syringe through the septum. Then the flask was placed in a thermostated oil bath and heated at 100 °C with vigorous stirring within 24 h, and then cooled to 20 °C. The reaction mixture was neutralized with concentrated aqueous HCl to pH 6–7 under an argon atmosphere and then centrifuged. The precipitate separated was washed sequentially with MeCN ( $3 \times 4$  mL) and acetone ( $3 \times 4$  mL). The centrifuged solution combined with washes was evaporated to dryness *in vacuo*. The residue obtained was extracted with hot *n*-heptane ( $5 \times 4$  mL) at 90–100 °C, and the extract was evaporated to dryness *in vacuo* (rotary evaporator) at room temperature. The residue obtained was treated with hexane ( $\sim 100$   $\mu\text{L}$ ) at  $-15$  °C, and the precipitate formed was collected by filtration and recrystallized from heptane to give 23 mg (47%) of compound **7a- $^{18}\text{O}$** . Colorless needles, mp 106–108 °C.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  3.42 (s, 6H,  $2\text{CH}_3$ ), 6.96–6.99 (m, 2H, Ar), 7.09–7.12 (m, 2H, Ar).  $^{13}\text{C}\{^1\text{H}\}$  NMR



(CDCl<sub>3</sub>):  $\delta$  27.3, 107.4, 121.3, 130.1, 154.8. ESI-MS(TOF) calcd for C<sub>9</sub>H<sub>11</sub>N<sub>2</sub><sup>18</sup>O [M + H]<sup>+</sup>  $m/z$  165.0908, found  $m/z$  165.0906.

**Reaction of complex 6a with KOH.** A mixture of a solution of compound **6a** (181 mg, 0.3 mmol) in 1,4-dioxane (1.5 mL) and 3 M aqueous KOH solution (1 mL, 3 mmol) was vigorously stirred in a Teflon screw cap tube at 100 °C within 20 h, and then cooled to 20 °C. The light blue-green precipitate of Ni(OH)<sub>2</sub> was separated by centrifugation, washed sequentially with hot MeCN (3 × 5 mL), hot DMF (5 mL), water (3 × 5 mL), and again with MeCN (5 mL), then dried at 80 °C *in vacuo* to constant weight to give 25 mg (91%) of Ni(OH)<sub>2</sub>. After the separation of Ni(OH)<sub>2</sub>, the reaction mixture was analyzed by HPLC and GC-MS to determine the yield of azolone **7a**, then diluted with water (30 mL) and extracted with benzene (5 × 10 mL). The extract was evaporated to dryness *in vacuo*. The dark oily residue obtained was dissolved in 5 mL of 10% aqueous HCl solution, the solution was treated with charcoal and evaporated *in vacuo* to dryness to give whitish-pink crystals of *N,N'*-dimethylbenzene-1,2-diamine dihydrochloride (**8a** × 2HCl). Yield 98 mg (78%), mp 167–170 °C. <sup>1</sup>H NMR (DMSO-*d*<sub>6</sub>):  $\delta$  2.77 (s, 6H, 2CH<sub>3</sub>), 7.00–7.06 (m, 4H, Ar). <sup>13</sup>C {<sup>1</sup>H} NMR (DMSO-*d*<sub>6</sub>):  $\delta$  32.2, 118.1, 123.3 (the signal of two aromatic carbons is broadened and merged into the background). ESI-MS(TOF) calcd for C<sub>8</sub>H<sub>13</sub>N<sub>2</sub> [M – HCl – Cl]<sup>+</sup>  $m/z$  137.1073, found  $m/z$  137.1073.

**Reaction of compound 1a with *t*-BuOK.** A mixture of compound **1a** (0.411 g, 1.5 mmol), 1,4-dioxane (25 mL) and *t*-BuOK (1.68 g, 15 mmol) was vigorously stirred in a Teflon screw cap tube at 100 °C within 20 h. According to the HPLC and GC-MS analyses, the main reaction products were diamine **8a** (~82% HPLC yield) and 1,3-dimethyl-benzimidazol-2-one **7a** (~10% HPLC yield). The reaction mixture was neutralized with 10% HCl to pH ~ 10, diluted with water (80 mL) and extracted with benzene (4 × 50 mL). The extract was dried with anhydrous Na<sub>2</sub>SO<sub>4</sub> and evaporated to dryness *in vacuo*. The dark oily residue obtained was dissolved in 30 mL of hot 10% aqueous HCl solution. The resulted solution was treated with charcoal and evaporated to dryness *in vacuo*. The solid obtained was recrystallized from MeCN to give whitish-pink crystals of *N,N'*-dimethylbenzene-1,2-diamine dihydrochloride (**8a** × 2HCl), yield 204 mg (65%). The physical and spectral characteristics of the product obtained are identical to the product obtained from the reaction of compound **6a** with KOH.

A solution of 40 mg of **8a** × 2HCl in 10% aqueous KOH (0.5 mL) was extracted by C<sub>6</sub>D<sub>6</sub> (1 mL). The extract of *N,N'*-dimethylbenzene-1,2-diamine (**8a**, free base) was dried by Na<sub>2</sub>SO<sub>4</sub> and then analyzed by NMR. <sup>1</sup>H NMR (C<sub>6</sub>D<sub>6</sub>):  $\delta$  2.41 (s, 6H, 2CH<sub>3</sub>), 6.62–6.65 (m, 2H, Ar), 6.98–7.01 (m, 2H, Ar). <sup>13</sup>C {<sup>1</sup>H} NMR (C<sub>6</sub>D<sub>6</sub>):  $\delta$  30.7, 110.9, 119.6, 138.8. ESI-MS(TOF) calcd for C<sub>8</sub>H<sub>13</sub>N<sub>2</sub> [M + H]<sup>+</sup>  $m/z$  137.1073, found  $m/z$  137.1074.

**Reaction of compound 1c with *t*-BuOK.** The reaction procedure was analogous to the one for the compound **1a** described above. The compound **1c** (0.495 g, 1.5 mmol) afforded diamine **8b** (~83% HPLC yield) and azolone **7c** (~8% HPLC yield). The diamine **8b** was isolated as *N,N'*-dipropylbenzene-1,2-diamine dihydrochloride (**8b** × 2HCl), yield 179 mg (45%), mp 153–156 °C. <sup>1</sup>H NMR (DMSO-*d*<sub>6</sub>):  $\delta$  0.94 (t, *J* = 7.4 Hz, 6H, 2CH<sub>3</sub>), 1.65–1.70 (m, 4H, 2CH<sub>2</sub>), 3.06–3.09 (m, 4H, 2CH<sub>2</sub>), 6.98–7.05 (m,

4H, Ar). ESI-MS(TOF) calcd for C<sub>12</sub>H<sub>21</sub>N<sub>2</sub> [M – HCl – Cl]<sup>+</sup>  $m/z$  193.1699, found  $m/z$  193.1690.

A solution of 40 mg of the dihydrochloride (**8b** × 2HCl) in 0.5 mL of 10% aqueous KOH was extracted by C<sub>6</sub>D<sub>6</sub> (1 mL). The extract of *N,N'*-dipropylbenzene-1,2-diamine (**8b**, free base) was dried by Na<sub>2</sub>SO<sub>4</sub> and then analyzed by NMR. <sup>1</sup>H NMR (C<sub>6</sub>D<sub>6</sub>):  $\delta$  0.80 (t, *J* = 7.4 Hz, 6H, 2CH<sub>3</sub>), 1.33–1.41 (m, 4H, 2CH<sub>2</sub>), 2.78–2.80 (m, 4H, 2CH<sub>2</sub>), 6.70–6.73 (m, 2H, Ar), 6.97–7.01 (m, 2H, Ar). <sup>13</sup>C {<sup>1</sup>H} NMR (C<sub>6</sub>D<sub>6</sub>):  $\delta$  11.9, 23.1, 46.4, 112.4, 119.7, 138.1.

**Reaction of compound 1f with *t*-BuOK.** Based on the same procedure as indicated for the compound **1a** above, compound **1f** (0.467 g, 1.5 mmol) afforded diamine **8c** (~85% HPLC yield) and azolone **7f** (~10% HPLC yield). The diamine **8c** was isolated as *N,N'*-dibutylbenzene-1,2-diamine diperchlorate (**8c** × 2HClO<sub>4</sub>), yield 633 mg (67%), mp 135–138 °C. <sup>1</sup>H NMR (DMSO-*d*<sub>6</sub>):  $\delta$  0.91 (t, *J* = 7.2 Hz, 6H, 2CH<sub>3</sub>), 1.34–1.41 (m, 4H, 2CH<sub>2</sub>), 1.58–1.61 (m, 4H, 2CH<sub>2</sub>), 3.14–3.17 (m, 4H, 2CH<sub>2</sub>), 7.00–7.05 (m, 4H, Ar). <sup>13</sup>C {<sup>1</sup>H} NMR (DMSO-*d*<sub>6</sub>):  $\delta$  13.6, 19.4, 28.9, 66.3, 118.6, 123.4 (the signal of two aromatic carbons is broadened and merged into the background). ESI-MS(TOF) calcd for C<sub>14</sub>H<sub>25</sub>N<sub>2</sub> [M – HClO<sub>4</sub> – ClO<sub>4</sub>]<sup>+</sup>  $m/z$  221.2012, found  $m/z$  221.2008.

## Influence of the O–NHC coupling reaction on the catalytic activity of Pd–NHC complexes in the Mizoroki–Heck reaction

**Preparation of the catalyst (method A).** Compound **2j** (16 mg, 25 μmol) was dissolved in pyridine (1 mL) at 30 °C within 15 min. Then, 0.1 mL (2.5 μmol of [Pd]) of the precatalyst solution was added immediately as the catalyst to the reaction mixture of the Mizoroki–Heck reaction.

**Preparation of the catalyst (method B).** A mixture of compound **2j** (16 mg, 25 μmol) and *t*-BuOK (28 mg, 0.25 mmol) in pyridine (1 mL) was heated for 10 min at 100 °C with vigorous stirring (Scheme 9), then cooled to room temperature and neutralized by the addition of pyridine hydrochloride (30 mg, 0.26 mmol). 0.1 mL (2.5 μmol of [Pd]) of the resultant mixture was added as the catalyst to the reaction mixture of the Mizoroki–Heck reaction.

A 7 mL screw-capped glass tube equipped with a magnetic stirring bar was charged with K<sub>2</sub>CO<sub>3</sub> (138 mg, 1 mmol), PhI (102 mg, 0.5 mmol), *n*-butyl acrylate (96 mg, 0.75 mmol) and naphthalene (12.8 mg, 0.1 mmol) in DMF (0.9 mL). A solution of the corresponding Pd catalyst (2.5 μmol, 0.5 mol%) in pyridine (0.1 mL) prepared according to the method A or B was added to the reaction tube. The tube was sealed with a screw cap, fitted with a septum and placed immediately in a thermostated oil bath with vigorous stirring at 60 °C, and that instant was taken as the starting time of the reaction. After 20 hours, samples of the reaction mixtures (1 μL) were taken up from the tubes, diluted with MeCN (1 mL) and then subjected to analysis. The yields (%) of coupling product **12** were determined by GC-MS (naphthalene as internal standard).

## Influence of the O–NHC coupling reaction on the catalytic activity of Pd–NHC complexes in the Suzuki–Miyaura reaction

**Preparation of the catalyst (method A).** Compound **2j** (4 mg, 6.25 μmol) was dissolved in DMF (0.1 mL) at 25 °C within





15 min. Then, 10  $\mu\text{L}$  of the solution (0.625  $\mu\text{mol}$  of  $[\text{Pd}]$ ) was mixed with 1,4-dioxane (0.1 mL), and a solution of pyridine (0.5 mg, 6.3  $\mu\text{mol}$ ) in *i*-PrOH (0.1 mL). The resultant mixture was added immediately as the catalyst to the reaction mixture.

**Preparation of the catalyst (method B).** Compound **2j** (4 mg, 6.25  $\mu\text{mol}$ ) was dissolved in DMF (0.1 mL) at 25  $^{\circ}\text{C}$  within 15 min. Then, a mixture of 10  $\mu\text{L}$  (0.625  $\mu\text{mol}$  of  $[\text{Pd}]$ ) of the precatalyst solution, 1,4-dioxane (0.1 mL) and *t*-BuOK (0.7 mg, 6.25 mmol) was heated for 10 min at 100  $^{\circ}\text{C}$  with vigorous stirring, then cooled to room temperature and neutralized by addition of a solution of pyridine hydrochloride (0.7 mg, 6.3  $\mu\text{mol}$ ) in *i*-PrOH (0.1 mL). The resultant mixture was added as the catalyst to the reaction mixture of the Suzuki–Miyaura Reaction.

A 7 mL screw-capped glass tube equipped with a magnetic stirring bar was charged with a solution of 4-bromo-*N,N*-dimethylaniline (50 mg, 0.25 mmol), phenylboronic acid (43 mg, 0.35 mmol) and naphthalene (16 mg, 0.125 mmol), *i*-PrOH (0.5 mL), and a solution of KOH (28 mg, 0.5 mmol) in  $\text{H}_2\text{O}$  (0.4 mL). A solution of the Pd catalyst (0.625  $\mu\text{mol}$ , 0.25 mol%) prepared according to the method A or B was added to the reaction tube. The tube was purged with argon and sealed with a screw cap, fitted with a septum and placed immediately in a thermostated oil bath with vigorous stirring at 80  $^{\circ}\text{C}$ , and that instant was taken as the starting time of the reaction. After 2 hours, samples of the reaction mixtures (1  $\mu\text{L}$ ) were taken up from the tubes, diluted with MeCN (1 mL) and then subjected to analysis. The yields (%) of coupling product **14** were determined by GC-MS (naphthalene as internal standard).

### Influence of the O–NHC coupling reaction on the catalytic activity of Pd–NHC complexes in the arylation of ketones

**Preparation of the catalyst (method A).** Compound **2i** (16 mg, 25  $\mu\text{mol}$ ) was dissolved in 1,4-dioxane (0.5 mL) at 30  $^{\circ}\text{C}$  within 15 min. Then, 0.1 mL (5.0  $\mu\text{mol}$  of  $[\text{Pd}]$ ) of the precatalyst solution was added immediately as the catalyst to the reaction mixture.

**Preparation of the catalyst (method B).** A mixture of compound **2i** (16 mg, 25  $\mu\text{mol}$ ) and *t*-BuOK (28 mg, 0.25 mmol) in 1,4-dioxane (0.5 mL) was heated for 10 min or 3 h at 100  $^{\circ}\text{C}$  with vigorous stirring (Scheme 9), then cooled to room temperature and neutralized by the addition of pyridine hydrochloride (30 mg, 0.26 mmol). 0.1 mL (5.0  $\mu\text{mol}$  of  $[\text{Pd}]$ ) of the resultant mixture was added as the catalyst to the reaction mixture.

A 7 mL screw-capped glass tube equipped with a magnetic stirring bar was charged with a solution of *t*-BuONa (53 mg, 0.55 mmol), PhCl (56 mg, 0.5 mmol), acetophenone (66 mg, 0.55 mmol) and naphthalene (12.8 mg, 0.1 mmol) in 1,4-dioxane (1.9 mL). A solution of the Pd catalyst (5  $\mu\text{mol}$ , 1 mol%) prepared according to the method A or B was added to the reaction tube. The tube was purged with argon and sealed with a screw cap, fitted with a septum and placed immediately in a thermostated oil bath with vigorous stirring at 100  $^{\circ}\text{C}$ , and that instant was taken as the starting time of the reaction. After 3 hours, samples of the reaction mixtures (1  $\mu\text{L}$ ) were taken up from the tubes, diluted with MeCN (1 mL) and then subjected to analysis. The

yields (%) of coupling product **16** were determined by GC-MS (naphthalene as internal standard).

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The present study was supported by the Russian Science Foundation RSF grant no. 14-23-00078 (mechanistic study and investigation of the catalytic reactions) and by the Russian Foundation for Basic Research, RFBR grants 16-29-10786 (synthesis and transformations of metal complexes) and 17-33-50047 (ESI-MS studies of reaction intermediates). The authors also thank the Shared Research Center “Nanotechnologies” of the Platov South-Russian State Polytechnic University and the Department of Structural Studies of Zelinsky Institute of Organic Chemistry for analytical services. The authors are grateful to Olga E. Eremina (Chemistry Department, Lomonosov Moscow State University) for the Raman spectroscopy analysis.

## References

- (a) W. A. Herrmann, *Angew. Chem., Int. Ed.*, 2002, **41**, 1290; (b) G. C. Fortman and S. P. Nolan, *Chem. Soc. Rev.*, 2011, **40**, 5151; (c) C. Valente, S. Çalimsiz, K. H. Hoi, D. Mallik, M. Sayah and M. G. Organ, *Angew. Chem., Int. Ed.*, 2012, **51**, 3314; (d) M. N. Hopkinson, C. Richter, M. Schedler and F. Glorius, *Nature*, 2014, **510**, 485; (e) *N-Heterocyclic Carbenes: From Laboratory to Curiosities to Efficient Synthetic Tools*, ed. S. Díez-González, Royal Society of Chemistry, London, UK, 2017; (f) A. Nasr, A. Winkler and M. Tamm, *Coord. Chem. Rev.*, 2016, **316**, 68; (g) E. Peris, *Chem. Rev.*, 2017, DOI: 10.1021/acs.chemrev.6b00695; (h) V. Ritleng, M. Henrion and M. J. Chetcuti, *ACS Catal.*, 2016, **6**, 890; (i) N. Hazari, P. R. Melvin and M. M. Beromi, *Nat. Rev. Chem.*, 2017, **1**, 0025; (j) S. Hameury, P. de Fremont and P. Braunstein, *Chem. Soc. Rev.*, 2017, **46**, 632; (k) *Hydrofunctionalization*, ed. V. P. Ananikov and M. Tanaka, Springer, Berlin, Heidelberg, 2013; (l) I. P. Beletskaya and V. P. Ananikov, *Chem. Rev.*, 2011, **111**, 1596.
- (a) K. C. Nicolaou, P. G. Bulger and D. Sarlah, *Angew. Chem., Int. Ed.*, 2005, **44**, 4442; (b) B. Carsten, F. He, H. J. Son, T. Xu and L. Yu, *Chem. Rev.*, 2011, **111**, 1493; (c) J.-P. Corbet and G. Mignani, *Chem. Rev.*, 2006, **106**, 2651; (d) C. Torborg and M. Beller, *Adv. Synth. Catal.*, 2009, **351**, 3027.
- (a) C. M. Crudden and D. P. Allen, *Coord. Chem. Rev.*, 2004, **248**, 2247; (b) H. Jacobsen, A. Correa, A. Poater, C. Costabile and L. Cavallo, *Coord. Chem. Rev.*, 2009, **253**, 687; (c) T. Dröge and F. Glorius, *Angew. Chem., Int. Ed.*, 2010, **49**, 6940.
- (a) C. Valente, M. Pompeo, M. Sayah and M. G. Organ, *Org. Process Res. Dev.*, 2014, **18**, 180; (b) P. Ruiz-Castillo and S. L. Buchwald, *Chem. Rev.*, 2016, **116**, 12564.





- 5 Literature search *via* SciFinder and Scopus revealed hundreds of studies in which M/NHC catalyzed reactions were performed in the presence of excess of a strong base like *tert*-BuOK, *tert*-BuONa, KOH, NaOH (sometimes, up to 3 mol of the base per mol of coupling reagent was used).
- 6 (a) S. Kotha, K. Lahiri and D. Kashinath, *Tetrahedron*, 2002, **58**, 9633; (b) C. G. Newton, S.-G. Wang, C. C. Oliveira and N. Cramer, *Chem. Rev.*, 2017, **117**, 8908; (c) I. P. Beletskaya and A. V. Cheprakov, *Chem. Rev.*, 2000, **100**, 3009; (d) R. I. McDonald, G. Liu and S. S. Stahl, *Chem. Rev.*, 2011, **111**, 2981.
- 7 (a) A. Tudose, L. Delaude, B. André and A. Demonceau, *Tetrahedron Lett.*, 2006, **47**, 8529; (b) Y. Schramm, M. Takeuchi, K. Semba, Y. Nakao and J. F. Hartwig, *J. Am. Chem. Soc.*, 2015, **137**, 12215; (c) A. L. Gottumukkala, J. G. de Vries and A. J. Minnaard, *Chem.-Eur. J.*, 2011, **17**, 3091; (d) C. Jahier, O. V. Zatolochnaya, N. V. Zvyagintsev, V. P. Ananikov and V. Gevorgyan, *Org. Lett.*, 2012, **14**, 2846; (e) O. V. Zatolochnaya, E. G. Gordeev, C. Jahier, V. P. Ananikov and V. Gevorgyan, *Chem.-Eur. J.*, 2014, **20**, 9578.
- 8 L. Xu, L. W. Chung and Y.-D. Wu, *ACS Catal.*, 2016, **6**, 483.
- 9 (a) J. Pytkowicz, S. Roland, P. Mangeney, G. Meyer and A. Jutand, *J. Organomet. Chem.*, 2003, **678**, 166; (b) S. Raoufmoghaddam, S. Mannathan, A. J. Minnaard, J. G. de Vries and J. N. H. Reek, *Chem.-Eur. J.*, 2015, **21**, 18811.
- 10 (a) M. S. Viciu, R. F. Germaneau, O. Navarro-Fernandez, E. D. Stevens and S. P. Nolan, *Organometallics*, 2002, **21**, 5470; (b) N. Marion, O. Navarro, J. Mei, E. D. Stevens, N. M. Scott and S. P. Nolan, *J. Am. Chem. Soc.*, 2006, **128**, 4101; (c) A. J. DeAngelis, P. G. Gildner, R. Chow and T. J. Colacot, *J. Org. Chem.*, 2015, **80**, 6794; (d) P. R. Melvin, D. Balcells, N. Hazari and A. Nova, *ACS Catal.*, 2015, **5**, 5596.
- 11 O. V. Khazipov, M. A. Shevchenko, A. Y. Chernenko, A. V. Astakhov, D. V. Pasyukov, D. B. Eremin, Y. V. Zubavichus, V. N. Khrustalev, V. M. Chernyshev and V. P. Ananikov, *Organometallics*, 2018, **37**, 1483.
- 12 (a) R. Garrido, P. S. Hernández-Montes, Á. Gordillo, P. Gómez-Sal, C. López-Mardomingo and E. de Jesús, *Organometallics*, 2015, **34**, 1855; (b) E. Steeples, A. Kelling, U. Schilde and D. Esposito, *New J. Chem.*, 2016, **40**, 4922.
- 13 (a) J. C. Lewis, S. H. Wiedemann, R. G. Bergman and J. A. Ellman, *Org. Lett.*, 2004, **6**, 35; (b) F. Zeng and Z. Yu, *J. Org. Chem.*, 2006, **71**, 5274; (c) Y.-M. Liu, Y.-C. Lin, W.-C. Chen, J.-H. Cheng, Y.-L. Chen, G. P. A. Yap, S.-S. Sun and T.-G. Ong, *Dalton Trans.*, 2012, **41**, 7382.
- 14 A. V. Astakhov, O. V. Khazipov, E. S. Degtyareva, V. N. Khrustalev, V. M. Chernyshev and V. P. Ananikov, *Organometallics*, 2015, **34**, 5759.
- 15 (a) A. M. Zawisza and J. Muzart, *Tetrahedron Lett.*, 2007, **48**, 6738; (b) M. Górna, M. S. Szulmanowicz, A. Gniewek, W. Tylus and A. M. Trzeciak, *J. Organomet. Chem.*, 2015, **785**, 92.
- 16 A. A. Konstantinchenko, A. S. Morkovnik, A. F. Pozharskii and B. A. Tertov, *Chem. Heterocycl. Compd.*, 1985, **21**, 1398.
- 17 (a) L. S. Santos, *Eur. J. Org. Chem.*, 2008, **2008**, 235; (b) V. V. Kachala, L. L. Khemchyan, A. S. Kashin, N. V. Orlov, A. A. Grachev, S. S. Zaleskiy and V. P. Ananikov, *Russ. Chem. Rev.*, 2013, **82**, 648; (c) K. L. Vikse, Z. Ahmadi and J. S. McIndoe, *Coord. Chem. Rev.*, 2014, **279**, 96; (d) C. Iacobucci, S. Reale and F. De Angelis, *Angew. Chem., Int. Ed.*, 2016, **55**, 2980.
- 18 (a) B. R. M. Lake, M. R. Chapman and C. E. Willans, in *Organomet. Chem.*, The Royal Society of Chemistry, 2016, vol. 40, p. 107; (b) D. J. Nelson, J. M. Praetorius and C. M. Crudden, in *N-Heterocyclic Carbenes: From Laboratory Curiosities to Efficient Synthetic Tools*, The Royal Society of Chemistry, 2017, vol. 27, ch. 2, p. 46; (c) A. V. Astakhov, O. V. Khazipov, A. Y. Chernenko, D. V. Pasyukov, A. S. Kashin, E. G. Gordeev, V. N. Khrustalev, V. M. Chernyshev and V. P. Ananikov, *Organometallics*, 2017, **36**, 1981; (d) E. G. Gordeev, D. B. Eremin, V. M. Chernyshev and V. P. Ananikov, *Organometallics*, 2017, **37**, 787.
- 19 (a) U. Siemeling, C. Farber, C. Bruhn, M. Leibold, D. Selent, W. Baumann, M. von Hopffgarten, C. Goedecke and G. Frenking, *Chem. Sci.*, 2010, **1**, 697; (b) D. Martin, N. Lassauque, B. Donnadieu and G. Bertrand, *Angew. Chem., Int. Ed.*, 2012, **51**, 6172.
- 20 D. B. Eremin and V. P. Ananikov, *Coord. Chem. Rev.*, 2017, **346**, 2.
- 21 O. E. Eremina, A. V. Sidorov, T. N. Shekhovtsova, E. A. Goodilin and I. A. Veselova, *ACS Appl. Mater. Interfaces*, 2017, **9**, 15058.
- 22 M. J. Saif and K. R. Flower, *Transition Met. Chem.*, 2013, **38**, 113.
- 23 R. Rubbiani, I. Kitanovic, H. Alborzinia, S. Can, A. Kitanovic, L. A. Onambele, M. Stefanopoulou, Y. Geldmacher, W. S. Sheldrick, G. Wolber, A. Prokop, S. Wölfl and I. Ott, *J. Med. Chem.*, 2010, **53**, 8608.
- 24 J. A. V. Er, A. G. Tennyson, J. W. Kamplain, V. M. Lynch and C. W. Bielawski, *Eur. J. Inorg. Chem.*, 2009, **2009**, 1729.
- 25 H. V. Huynh, Y. Han, J. H. H. Ho and G. K. Tan, *Organometallics*, 2006, **25**, 3267.
- 26 Y. Han, H. V. Huynh and G. K. Tan, *Organometallics*, 2007, **26**, 6447.
- 27 Y. Shi, Z. Cai, Y. Peng, Z. Shi and G. Pang, *J. Chem. Res.*, 2011, **35**, 161.
- 28 C. J. O'Brien, E. A. B. Kantchev, C. Valente, N. Hadei, G. A. Chass, A. Lough, A. C. Hopkinson and M. G. Organ, *Chem.-Eur. J.*, 2006, **12**, 4743.
- 29 H. V. Huynh, J. H. H. Ho, T. C. Neo and L. L. Koh, *J. Organomet. Chem.*, 2005, **690**, 3854.
- 30 M. Bouché, G. Dahm, A. Maisse-François, T. Achard and S. Bellemin-Laponnaz, *Eur. J. Inorg. Chem.*, 2016, **2016**, 2828.
- 31 Y. Han, H. V. Huynh and G. K. Tan, *Organometallics*, 2007, **26**, 4612.
- 32 H. V. Huynh, C. Holtgrewe, T. Pape, L. L. Koh and E. Hahn, *Organometallics*, 2006, **25**, 245.
- 33 I. M. AlNashef, M. A. Hashim, F. S. Mjalli, M. Q. A.-h. Ali and M. Hayyan, *Tetrahedron Lett.*, 2010, **51**, 1976.



- 34 J. B. H. Hřebabecký, *Collect. Czech. Chem. Commun.*, 1985, **50**, 779.
- 35 M. Guiliano, G. Mille, J. Chouteau, J. Kister and J. Metzger, *Appl. Spectrosc.*, 1981, **35**, 486.
- 36 Z. Wu, Z. An, X. Chen and P. Chen, *Org. Lett.*, 2013, **15**, 1456.
- 37 S. T. Manjare, H. B. Singh and R. J. Butcher, *Tetrahedron*, 2012, **68**, 10561.
- 38 J. Duchek and A. Vasella, *Helv. Chim. Acta*, 2011, **94**, 977.
- 39 G. Vernin, H. Domlog, C. Siv, J. Metzger and A. K. El-Shafei, *J. Heterocycl. Chem.*, 1981, **18**, 85.
- 40 (a) J.-P. Li, Y. Huang, M.-S. Xie, G.-R. Qu, H.-Y. Niu, H.-X. Wang, B.-W. Qin and H.-M. Guo, *J. Org. Chem.*, 2013, **78**, 12629; (b) Y. Li, W. Du and W.-P. Deng, *Tetrahedron*, 2012, **68**, 3611; (c) H. M. Lima and C. J. Lovely, *Org. Lett.*, 2011, **13**, 5736; (d) Y. Kandri Rodi, F. Ouazzani Chahdi, E. M. Essassi, S. V. Luis, M. Bolte and L. El Ammari, *Acta Crystallogr., Sect. E: Struct. Rep. Online*, 2011, **67**, o3234.
- 41 W. Zeng, E. Wang, R. Qiu, M. Sohail, S. Wu and F.-X. Chen, *J. Organomet. Chem.*, 2013, **743**, 44.

