



Cite this: *J. Mater. Chem. A*, 2021, 9, 19589

Applications of MAX phases and MXenes as catalysts

Iuliana M. Chirica,^{ab} Anca G. Mirea,^a Ștefan Neațu,^a Mihaela Florea,^{*a} Michel W. Barsoum^{bc} and Florentina Neațu^{da}

MAX phases and MXenes are important materials that have recently gained great popularity due to their special properties, which render them particularly useful in many applications, including catalytic ones. This can be seen in the large number of publications that appear annually on these materials and their applications. This review aims to evaluate MAX phases and MXenes as materials for heterogeneous, non-electrocatalytic, catalytic applications. The review begins with a brief introduction to the MAX phase and MXene properties that recommend them as potential materials for heterogeneous catalytic applications, followed by four sections grouped according to the processes in which they have already proven effective. These include supports to activate the C–H or C–O bonds in applications such as dehydrogenation of light or aromatic alkanes, methanol formation from CH₄, dry reforming, and CO oxidation or the water gas shift reaction (Section 2), and their use in fine chemical reactions (Section 3) and in chemical degradation (Section 4). The last section deals with photocatalytic applications (Section 5). The review ends by highlighting the huge potential of these materials for a wide range of heterogeneous catalytic applications as well as the challenges ahead.

Received 14th May 2021

Accepted 28th July 2021

DOI: 10.1039/d1ta04097a

rsc.li/materials-a

1. Introduction

The MAX phases (M_{n+1}AX_n) and their derivatives, MXenes (M_{n+1}X_nT_x), (with $n = 1-4$, M = early transition metal, A = A-group element, X = carbon or nitrogen and T_x = various surface terminations, such as –O, –OH and –F) are a relatively new class of materials that have been discovered in the last two

decades.¹⁻³ They have impressed us by their multitude of physical and chemical properties. These materials manage to bring together two completely different classes of materials (ceramics and metals) by combining important properties from both classes, such as high thermal and electrical conductivity, mechanical strength and low density. Moreover, MAX phases also possess resistance to high temperatures or oxidation.

Presently, over 150 MAX phases⁴ and more than 30 MXenes with different compositions have been synthesized.⁵ The unique properties of MAX phases arise from their lamellar structure, metallic/covalent bonds, and the relatively weak bonds between the M and A layers.

^aNational Institute of Materials Physics, 405A Atomistilor Street, 077125 Magurele, Romania. E-mail: mihaela.florea@infim.ro; florentina.neatu@infim.ro

^bUniversity of Bucharest, Faculty of Physics, 405 Atomistilor Street, 077125 Magurele, Romania

^cDepartment of Materials Science & Engineering, Drexel University, Philadelphia, PA 19104, USA. E-mail: barsoumw@drexel.edu



Research team, part of the group Catalytic Material and Catalysis, at the National Institute of Materials Physics, Romania (NIMP) (<https://www.infim.ro>). From left to right: front row- Dr Mihaela Florea (senior researcher), Iuliana M. Chirica (PhD student), and Dr Anca G. Mirea (junior researcher) and back row- Dr Ștefan Neațu (senior researcher) and Dr Florentina Neațu (senior researcher). The research of the NIMP team is focused on the preparation, characterization and study of the physical properties of new materials connected to high technology products and devices. Their main research areas deal with heterogeneous catalysis, fuel cells and electrochemistry, materials surface science and energy conversion.

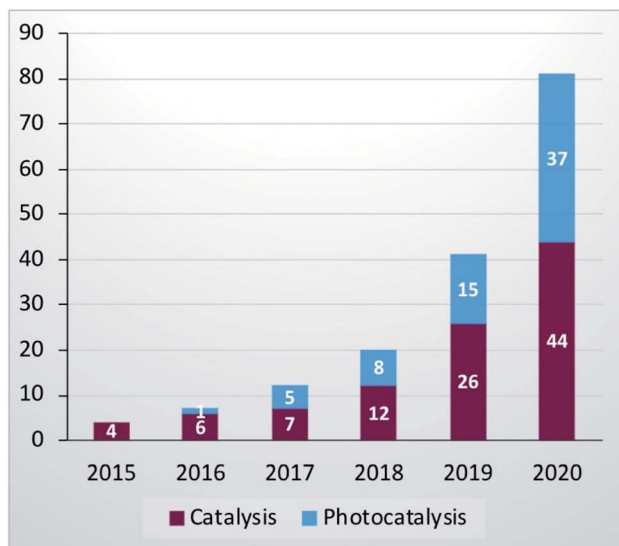


Fig. 1 MAX phase and MXene publications in catalysis and photocatalysis fields (data collected from <http://www.webofknowledge.com>) (May 2021, electrocatalysis was excluded).

The presence of oxygenated terminations preserves the high conductivity even in polar media.² Thus, as a result of all these interesting properties, MAX phases and MXenes are highly desirable and attractive materials for catalysis, but despite all evidence that recommends them as catalysts, their catalytic properties were investigated only recently⁶ and fortunately the interest is increasing exponentially (see Fig. 1) and is expected to grow considerably in the future.

Up to now, there are several excellent reviews about MXenes and MXene-based materials that focus on the preparation, properties, and potential applications.^{1–3,5,7–10} However, a comprehensive and systematic review on recent progress in the use of MAX phases and MXene-based materials in catalytic applications is lacking. In this review, we intend to present



Prof. Michel W. Barsoum is a Distinguished Professor in the Department of Materials Science and Engineering at Drexel University. He is an internationally recognized leader in the areas of MAX phases and their 2D derivatives, MXenes. He has published over 500 refereed publications. His *h* index is >110 and he was in the highly cited researchers list in 2018, 2019 and 2020. He is the author of

MAX Phases: Properties of Machinable Carbides and Nitrides and the leading textbook in his field, *Fundamentals of Ceramics*. In 2020, he was awarded the International Ceramics Prize for basic science by the World Academy of Ceramics.




Scheme 1 Application road map of the MAX phases and their MXene derivatives.

general aspects to be considered and to outline which are currently the most efficient catalytic systems based on these materials in: (i) catalytic processes centred on C–H and C–O activation, (ii) fine chemical reactions, (iii) catalytic degradation, and (iv) photocatalytic applications. An application road-map is depicted in Scheme 1. Note that there are already several review papers up to 2020 that cover photocatalytic materials.^{11–14} Here we thus focus only on the last two years (2020 and 2021). Moreover, in this review we do not discuss MAX phases and MXene materials as catalysts for electrochemical applications. Readers can refer to other comprehensive reviews in that area.^{15–17}

2. Processes based on C–H and C–O activation (theoretical and experimental studies)

The mind map illustrated in Scheme 2 summarizes the materials used in C–H and C–O bond activation and their corresponding catalytic reactions.

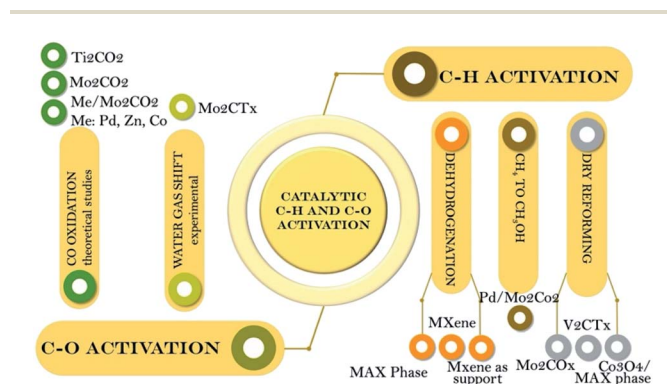

Scheme 2 Types of MAX phases and MXenes used in processes based on C–H and C–O activation.

2.1. C–H activation

2.1.1 Dehydrogenation reactions. As noted above, the physical, electrical and optical properties of the MAX phases and MXenes in general have been intensively studied recently. Much less work, however, has been devoted to their catalytic properties.

Direct dehydrogenation (DDH) and oxidative dehydrogenation (ODH) of hydrocarbons are important reactions for obtaining alkene monomers, that are, in turn, key intermediates in the polymer industry. Some of the important monomers include *n*-butene or 1,3-butadiene starting from *n*-butane¹⁸ or styrene synthesized from ethylbenzene.¹⁹

Usually these processes require high temperatures (~ 600 °C) and excess steam and suffer from catalyst deactivation due to the formation of coke. The MAX phases and MXenes show activity and long-term stability in these types of reactions.

2.1.2 MAX phases as catalysts. Ti_3AlC_2 is one of the first MAX phases which was reported to be a good catalyst in the *n*-butane ODH reaction with long-term stability.⁶

Oxidative reactions in general, and ODH in particular, are recognised to take place through redox mechanisms, meaning that the catalyst in a higher oxidation state oxidizes the reactants while it is being reduced, and the oxygen re-oxidizes the catalyst surface to restart a new cycle.^{20,21} This mechanism – also known as the Mars–van-Krevelen mechanism – is associated with oxide materials and usually metallic oxides or metals supported on metallic oxides.²²

The most intriguing part is that the MAX phases, while presenting combined metallic and ceramic properties, do not possess an oxygen lattice, which apparently is a prerequisite for oxidative reactions. However, Ti_3AlC_2 is not only active (24% conversion) in *n*-butane ODH, but it is also quite selective (a total selectivity of 50% for butenes and butadiene), which is a remarkable result.⁶ It is difficult to achieve active and selective catalysis simultaneously because conventional conditions to activate *n*-butane are too harsh and typically lead to total oxidation of *n*-butane (CO_2 and H_2O). The authors supposed that in the absence of an oxygen lattice, the adsorption of oxygen highly depends on the defect content of the surface oxide, which can also act as active sites. HRTEM data showed the presence of a large number of defects (point, domain or layer defects), while positron annihilation lifetime spectroscopic analyses confirmed the presence of Ti monovacancy defects and vacancy clusters and voids. The presence of a thin oxide layer on the surface (Al–Ti–O), with a high oxygen content (HRTEM, XPS, and EDX mapping) that is believed to have synergy with the electron reservoir below it, is believed to be responsible for the Ti_3AlC_2 activity in *n*-butane ODH. To confirm this assumption, computational evaluation of the possible mechanisms was considered, starting from the presumption that the stable ternary phase of Al_2TiO_5 is present on the surface and it is oxygen terminated. First, the DFT calculations showed that butane adsorbs relatively easily, through the formation of a C–O bond on the selected surface. Also, the DFT calculations indicated that the oxidative dehydrogenation of *n*-butane is energetically favourable on the MAX

phase surface and moreover, the presence of defects and the existence of superficial non-stoichiometric oxide surface layers rich in oxygen vacancies promote this material as a potential catalyst, enabling the transformation of *n*-butane into butene or/and butadiene.

2.1.3 MXenes as catalysts. Due to the similarities found between graphenes and MXenes ($\text{Ti}_3\text{C}_2\text{T}_x$), the abundance of functionalities on the surface (T_x) and the versatile properties of the latter, Diao *et al.*²³ investigated this class of materials in ethylbenzene DDH. The C-based materials have improved the overall process of ethylbenzene DDH and it is believed that active sites in the DDH reaction on 2D materials (*e.g.*, graphenes) are due to the flat surface and an enriched oxygenated functionality (*e.g.*, C=O) at the catalyst interface.^{24,25}

The results obtained by Diao *et al.*²³ showed that $\text{Ti}_3\text{C}_2\text{T}_x$ was not only suitable for this catalytic reaction, but also increased ethylbenzene's DDH activity to $92 \mu\text{mol m}^{-2} \text{h}^{-1}$, ~ 8 times higher than that of graphene. Combining experimental and theoretical first-principles calculations, it was concluded that the surface C–Ti–O groups and the layered structure of MXenes, that facilitate the mass transfer and adsorption–desorption processes, are responsible for the catalytic performance of $\text{Ti}_3\text{C}_2\text{T}_x$ in the ethylbenzene dehydrogenation reaction. Noteworthy, the selectivity of ethylbenzene DDH on $\text{Ti}_3\text{C}_2\text{T}_x$ was



Fig. 2 Reaction pathway and important structures of ethylbenzene dehydrogenation on $\text{Ti}_3\text{C}_2\text{O}_2$. Ti is shown in light gray, C in dark gray, O in red, and H in white. Reprinted with permission from ref. 23, copyright 2018 American Chemical Society.

97.5%, indicating very few side products. Thus, experimentally, the layered structure of MXenes has been demonstrated to bring an important value to the DDH reaction. Interestingly, the MAX phase precursor – Ti_3AlC_2 – reactivity was close to zero.

Fig. 2 shows the mechanism details of ethylbenzene dehydrogenation on $\text{Ti}_3\text{C}_2\text{T}_x$. The functional groups, T_x , found on the surface were C–Ti–O (high percentage), C–Ti–OH and C–Ti–F. At higher temperatures, the last two functionalities are prone to transform into C–Ti–O groups, that are believed to be responsible for the impressive activity of $\text{Ti}_3\text{C}_2\text{T}_x$. Additionally, $\text{Ti}_3\text{C}_2\text{T}_x$ has the advantage to remain active for a long time (40 h) without any deactivation. Transmission electron microscope, TEM, images evidenced the absence of coke on the surface, underscoring the stability of this material for ethylbenzene DDH. Besides the experimental evidence, the authors performed theoretical calculations to highlight both the MXene properties and the active sites responsible for this improved activity.²³

Computational studies also demonstrated that C–Ti–O can facilitate ethylbenzene dehydrogenation by approaching ethylbenzene in a parallel way and activating the C–H bond (0.66 eV) with O found on the surface. The second dehydrogenation is possible due to the abundance of O on the MXene surface and diffusion of hydrogen to neighbouring O (Fig. 2).

2.1.4 MXenes as a catalytic support. The presence of noble metals as nanoparticles on a support such as MXenes can favor the reduction of metal (M) from MXenes and/or the removal of surface functional groups.²⁶

Such an interaction drives the formation of bimetallic structures that form ordered intermetallic compounds (IMCs)

that are quite thermodynamically stable. This type of interaction can occur at lower temperatures facilitating the control of the noble metal particle size. For example, Li *et al.*²⁷ synthesized Pt_3Ti and Pt_3Nb IMCs with a Cu_3Au type structure by supporting Pt on $\text{Ti}_3\text{C}_2\text{T}_x$ and Nb_2CT_x MXenes, respectively. These compounds are extremely active in light alkane dehydrogenation. The reactivity is due to the Pt–M ordered intermetallic structures, which were evidenced by high resolution TEM microscopy (see Fig. 3), EXAFS and XANES.

These materials were tested in propane and isobutane dehydrogenation. In terms of activity, $\text{Pt}/\text{Ti}_3\text{C}_2\text{T}_x$ and $\text{Pt}/\text{Nb}_2\text{CT}_x$ were comparable with Pt/SiO_2 (15%), but they showed higher selectivity (90–95%) than standard catalysts (60%) in propylene formation. The influence of particle size on selectivity (smaller particles, higher selectivity) was excluded because the amount of intermetallic compounds was higher than that on Pt/SiO_2 . The increase in selectivity was related to the formation of IMCs. Contrary to classical catalysts, these materials, as explained by density functional theory, DFT, preserve the selectivity even at high values of activity and are stable under long-term reaction conditions. DFT showed that in the first step of the reaction, Pt(111) found in Pt/SiO_2 is more energetically favourable to adsorb and activate the C–H bond than $\text{Pt}_3\text{Ti}(111)$, but in the following steps, the formation of secondary products is not favoured on $\text{Pt}_3\text{Ti}(111)$. The experimental results and DFT calculations show that this is due to the lower barrier desorption of olefins compared with the deep dehydrogenation energy calculated on $\text{Pt}_3\text{Ti}(111)$, in contrast to the behaviour observed for Pt(111), thus explaining the high selectivity of Pt/MXene catalysts.

2.1.5 CH_4 to methanol. Besides the formation of ordered IMCs on MXenes, other theoretical studies have shown that supporting different noble metals on MXenes can facilitate the formation of single-atom catalysts (SACs). Surface defects of the supports have been found to play a crucial role in stabilizing single atoms.²⁸ It follows that MXenes, due to their 2D structure and defective surfaces, allow SAC formation and enhance the stability of SACs without affecting their activity or selectivity. For instance, by using DFT calculations, Wang *et al.*²⁹ demonstrated that single atoms of Pd monomers and dimers anchored on Mo_2CO_2 , where the oxygen in the formula indicates that the 2D system is O-terminated, can be stable and active for C–H bond activation. Moreover, the theory showed that Mo_2CO_2 could be an ideal support to anchor Pd dimers and can be considered a high-activity catalyst with sufficient structural stability for the direct conversion of methane to methanol. CH_4 and O_2 can stably adsorb on the Pd-dimer/ Mo_2CO_2 surfaces due to the existence of multiple adsorption sites.

2.1.6 Dry reforming. In 2020, the same material Mo_2CO_2 was dispersed on silica and found to provide high stability and catalytic activity in the dry reforming of methane, CH_4 (DRM)³⁰ (see eqn (1)).



Theoretical and experimental results indicated that CH_4 activation is the rate-limiting step, in agreement with the results

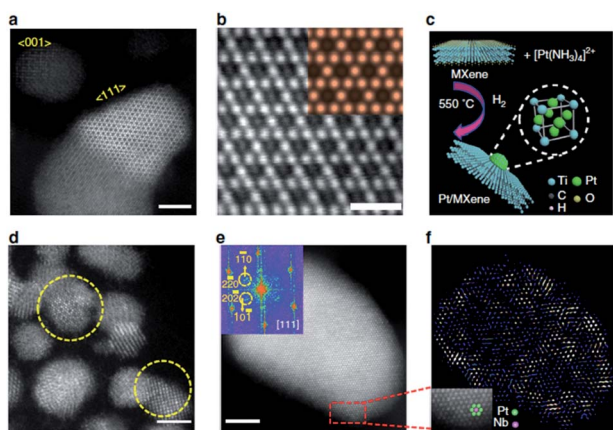


Fig. 3 TEM characterization of 1 wt% Pt/MXene catalysts. (a) Representative HAADF-STEM image of the 1% $\text{Pt}/\text{Ti}_3\text{C}_2\text{T}_x$ catalyst. (b) (111) surface of Pt_3Ti NPs. The inset shows a simulated STEM image of the $\text{Pt}_3\text{Ti}(111)$ surface. The simulated image is in good agreement with the experimental results. (c) Schematic illustration of reactive metal-support interactions in Pt/MXene catalysts and the structure of L12-ordered intermetallic Pt_3Ti . (d) Representative HAADF STEM image of the 1% $\text{Pt}/\text{Nb}_2\text{CT}_x$ catalyst. (e) Pt–Nb NPs viewed along [111], the inset shows the FFT pattern of the NPs. (f) IFFT pattern of the NPs in (e). The inset shows the enlarged image showing the superlattice of the NPs. Scale bars: (a, d, e) 2 nm, and (b) 500 pm. Reprinted from ref. 27 (open access).

of Wang *et al.*²⁹ The characterization data, such as XANES and XPS, suggested that 2D Mo_2CO_x contains Mo, with an average oxidation state of +4, that is the active phase for dry reforming of CH_4 . This was also supported by DFT calculations, which showed that CH_4 activation on oxygen sites to form $^*\text{OCH}_3$ and $^*\text{OH}$ is endergonic by 105 kJ mol^{-1} , which is 45 kJ mol^{-1} less favourable than CH_4 activation on the Mo sites of the same surface. Another key step in the dry reforming of CH_4 is the oxidation of either CH^* or C^* species on the oxycarbide surface by adsorbed oxygen (O^* or structural oxygen)³¹ to produce CO^* . In the case of 2D- Mo_2CO_x , and in contrast to metallic surfaces,³² DFT calculations showed that the preferred mechanism is the direct oxidation of adsorbed C^* by adsorbed O^* to form CO^* .

The idea of depositing MXenes on silica was to prevent the thermal transformation into bulk Mo_2C and MoO_2 phases, in this way opening new avenues for the application of 2D Mo-carbides and oxycarbides for high temperature heterogeneous catalysis. Indeed, the nanosheet morphology of 2D- Mo_2CO_x was maintained during catalysis and regeneration processes. Moreover, the 2D nature provides a very high utilization of Mo. For instance, when normalized by the weight of Mo, the initial CH_4 consumption rate of 2D- $\text{Mo}_2\text{CO}_x/\text{SiO}_2$ was $\sim 10\text{--}200$ times higher than the rates that have been reported for other Mo_2C based catalysts under similar reaction conditions.

This was not the case when multilayer V_2CT_x MXene ($m\text{-V}_2\text{CT}_x$) was used as the catalyst in DRM. Carrero *et al.* revealed that V_2CT_x MXene transforms during the reaction into an oxycarbide with the following composition: $\text{V}_2\text{O}_3\text{-V}_8\text{C}_7/m\text{-V}_2\text{CT}_x$ after exposure to CH_4 and CO_2 .³³ This oxy-carbide phase shows interesting activity for DRM, converting about 78% CH_4 and 82% CO_2 with CH_4 and CO_2 conversion rates of $153.4 \text{ mmol}_{\text{CH}_4} \text{ mol}_V^{-1} \text{ min}^{-1}$ and $178.2 \text{ mmol}_{\text{CO}_2} \text{ mol}_V^{-1} \text{ min}^{-1}$, respectively. The authors concluded that these results are comparable to those of Ni-based catalysts³⁴ and are about four times higher than those of the parent bulk V_2AlC MAX phase or VC.

The same V-based MXene was also reported as a good catalyst for dehydroaromatization of CH_4 .³⁵ The multi-layered, ML, 2D V_2CT_x transformed CH_4 in benzene at 700°C , with similar results to those of the benchmark Mo/ZSM-5 catalyst (11.8% activity, 4.84% yield at a formation rate of $1.9 \text{ mmol}_{\text{g}_{\text{cat}}}^{-1} \text{ h}^{-1}$). Besides the great importance of CH_4 dehydroaromatization (MDA) to produce liquid aromatics, this reaction is also extremely important from a fundamental point of view to establish the reaction mechanism for C–H activation. The

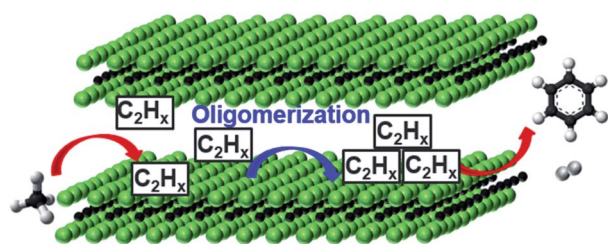


Fig. 4 MDA reaction scheme of $m\text{-V}_2\text{CT}_x$ MXene forming C_6H_6 and H_2 as the main reaction products. Reprinted with permission from ref. 35, copyright 2020 Wiley Online Library.

correlation of experimental data and operational Raman spectroscopy evidenced the presence of 2D-VC and 2D-V=O and the formation of C_2H_2 , H_2 , and benzene. The authors propose the V–C bond as an active site for C–H activation, followed by the formation of dimers, between the V_2CT_x layers ($\sim 7.0 \text{ \AA}$) (see Fig. 4). Oligomers and benzene formation requires acidic sites, which are associated with the presence of terminal functional groups (*e.g.*, OH and O^-) and/or are due to the presence of the unreacted V_2AlC MAX phase. Further studies are needed to conclusively better understand this reaction.

This material attracted interest due to the fact that it is stable at high temperatures.³⁶ Unfortunately, like in the benchmark catalyst, deactivation due to the deposition of graphitized C occurs. The deactivation rate of the MXene, however, is lower. Comparing the catalytic activity in DRM for the two MXenes, Mo_2CT_x and V_2CT_x , it was observed that Mo_2CT_x is not active at all, while V_2CT_x is active but only after the *in situ* transformation into an oxycarbide with the following composition: $\text{V}_2\text{O}_3\text{-V}_8\text{C}_7/m\text{-V}_2\text{CT}_x$. By supporting Mo_2CT_x on silica and after CO_2 treatment, a composite, $\text{Mo}_2\text{CO}_x/\text{SiO}_2$, that is as active as $\text{V}_2\text{O}_3\text{-V}_8\text{C}_7/m\text{-V}_2\text{CT}_x$ was obtained.

Based on the results obtained for direct dehydrogenation of *n*-butane, Ronda-Lloret *et al.*³⁷ surface modified Ti_2AlC with Co_3O_4 , to allow butane dry reforming. For butane dry reforming, the acidity of the material and also the good dispersion of the active sites are important considerations. Ti_2AlC has 10 times lower acidity than Al_2O_3 and its use as a support should generate a catalyst which deactivates slower than the benchmark catalysts ($\text{Co}_3\text{O}_4/\text{Al}_2\text{O}_3$ and $\text{Co}_3\text{O}_4/\text{TiO}_2$). Indeed, $\text{Co}_3\text{O}_4/\text{Ti}_2\text{AlC}$ has a lower activity (35%) than the $\text{Co}_3\text{O}_4/\text{Al}_2\text{O}_3$ (60%) catalyst, but has a much higher selectivity to CO and H_2 . The use of Ti_2AlC as a support generates special agglomeration of Co_3O_4 particles in the form of hollow spheres, 90–500 nm in diameter, with small voids (6–30 nm), that are unlike the Co_3O_4 particles supported on alumina or titania. The appearance of hollow spheres and small voids is associated with the special features of the MAX phase containing Ti–C and Ti–Al bonds, which allows the Kirkendall effect (different diffusion rates of the cations and anions during oxidation) to take place on the surface. Contrary to TiC, which decomposes to graphite and TiO_2 , Ti_2AlC is quite stable under dry reforming conditions. With time, the $\text{Co}_3\text{O}_4/\text{Ti}_2\text{AlC}$ surface becomes covered with carbon nanotubes, but the rate of coke deposition is much lower than that of the benchmark catalysts.

2.2. C–O activation

2.2.1 CO oxidation. Zhou *et al.*³⁸ carried out a theoretical study in which they studied CO oxidation on single Ti atoms anchored on a typical MXene monolayer, Ti_2CO_2 . The main idea was to employ Ti_2CO_2 monolayers in order to prevent the formation of Ti clusters, and therefore to increase the intrinsic activity, efficiency and stability of the catalyst. As shown in Fig. 5, which depicts the optimized energetically most favourable structures of O_2 and CO adsorbed on Ti-anchored on TiCO_2 , it is obvious that the catalyst could efficiently capture the

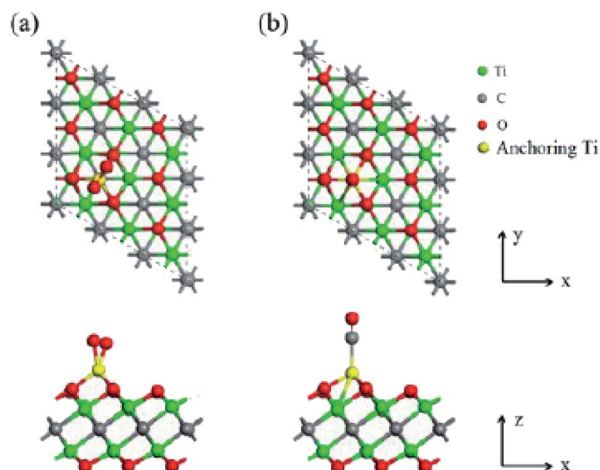


Fig. 5 Energetically most favorable structures of (a) O_2 and (b) CO adsorbed on Ti-anchored Ti_2CO_2 (top (upper) and side (lower) views). Reprinted with permission from ref. 38, copyright 2016 Royal Society of Chemistry.

reactants (O_2 and CO), and the adsorption energy of O_2 is higher than that of CO .

Data obtained using first-principles calculations indicated that the Eley–Rideal mechanism may be preferred under specific experimental conditions. Moreover, due to the fact that the energy barriers are comparable to many noble metal catalysts, the results demonstrated that Ti/Ti_2CO_2 does not need a noble metal to exhibit high activity for CO oxidation.

Another theoretical study of CO oxidation was reported using MXene as a support for single Pd atoms anchored on Mo_2CO_2 monolayers.³⁹ The key point of this study was the comparison of pristine and defective Mo_2CO_2 monolayers with an oxygen vacancy (denoted as $O_V-Mo_2CO_2$). In line with previous results,³⁸ $Pd/O_V-Mo_2CO_2$ was found to be highly active for CO oxidation and can achieve comparable catalytic activity to those containing noble metals. Moreover, the authors found that $Pd/O_V-Mo_2CO_2$, due to the fact that single Pd atoms can modify the electronic structure, has higher catalytic activity than iron embedded graphene,⁴⁰ copper embedded graphene,⁴¹ Pd-anchored graphene oxide and Pd-embedded vacancy graphene⁴² or $Pd@TiO_2(110)$ ⁴³ studied under the same reaction conditions. Contrary to the results obtained for Ti anchored on Mo_2CO_2 (ref. 38) for which the Eley–Rideal mechanism is preferred, for Pd supported on Mo_2CO_2 , among the three mechanisms studied, Eley–Rideal, Langmuir–Hinshelwood and termolecular Eley–Rideal, the latter is more preferable because of a small reaction barrier (0.49 eV) and can occur at lower temperatures. Moreover, the adsorbed CO molecules themselves could promote O_2 activation to easily form CO_2 , due to the fact that CO could transfer electrons to the $O_2-2\pi^*$ orbitals and induce O–O bond scission, in a process similar to the one found in gold cluster catalysts. It is demonstrated that defective MXenes may be used as supports for stable SACs, in agreement with other reported results.³⁸

Indeed, in 2019, also on the basis of first-principles calculations, different metals (M), such as Fe, Co, Ni, Cu, Zn,

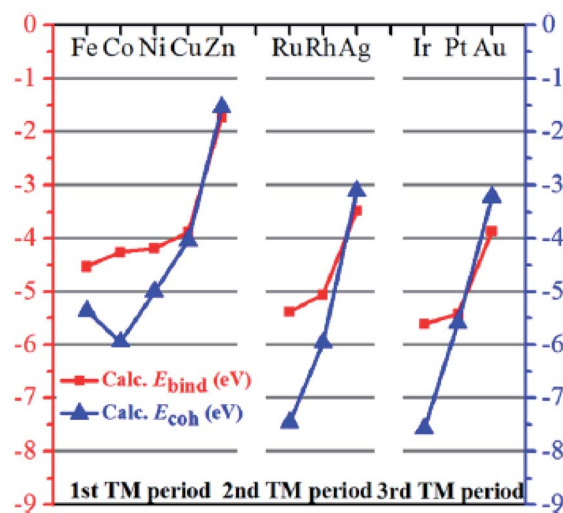


Fig. 6 Calculated binding energy (E_{bind} , red squares, left y-axis) and the corresponding bulk cohesive energy (E_{coh} , blue triangles, right y-axis) for $M/Mo_2CO_{2-\delta}$ ($M = Fe, Co, Ni, Cu, Zn, Ru, Rh, Ag, Ir, Pt, \text{ and } Au$). Reprinted with permission from ref. 44, copyright 2019 John Wiley and Sons.

Ru, Rh, Ag, Ir, Pt, and Au were decorated on defective $Mo_2CO_{2-\delta}$ monolayers and investigated as SAC candidates for a low-temperature CO oxidation reaction.⁴⁴ This study showed that the binding energy (E_{bind}) variations as the M atomic number increased (see Fig. 6) are similar for the three transition metal periods, but the M-surface binding becomes much weaker toward the end of the period, due to the fact that Cu, Zn, Ag, and Au have fully occupied d orbitals, so less free orbitals are available to participate in bonding with the MXene atoms.

From the calculated data it seems that $Zn/Mo_2CO_{2-\delta}$ has the weakest binding strength because of the fully filled 3d and 4s orbitals. Also, Zn is the only M that has a negative E_{diff} value (E_{diff} is the difference between the binding energy and cohesive energy), while the other metals (Fe, Co, Ni, Cu, Ru, Rh, Ir, and Pt) have positive E_{diff} values, indicating a strong tendency for clustering and they are, at least in this respect, not promising SAC candidates.


Therefore, based on well-established intuitive criteria concerning metal sintering, CO poisoning, and O_2 adsorption strength, the $Zn/Mo_2CO_{2-\delta}$ system was selected for reactivity calculations as a function of CO concentrations. The authors suggested that at low CO concentrations the oxidation reaction will predominantly proceed *via* the Eley–Rideal mechanism as it has a small energy barrier of 0.15 eV. In this case also, the main conclusion was that $Zn/Mo_2CO_{2-\delta}$ represents a potential candidate for low-temperature SAC applications that have a lower energy barrier for CO oxidation than that of noble metals and other 2D SAC systems.⁴⁴

Along the same lines, to design stable SACs, a systematic screening was performed using first principles calculations based on density functional theory.⁴⁵ More precisely, this study concerns different metal atoms such as Sc, Ti, V, Cr, Mn, Fe, Co, Ni, Cu, and Zn, that are deposited on different MXene

surfaces with a M_2C stoichiometry ($M = Ti, V, Cr, Zr, Nb, Mo, Hf, Ta, \text{ and } W$).⁴⁵ As in the previous case,⁴⁴ Zn atoms attached on MXene surfaces appear as the most stable SAC due to the fact that surface diffusion is hindered by moderate energy barriers. The calculation data also showed that all 3d metal studied atoms interact exothermically with MXene substrates and that the properties of the SAC can be tuned by suitably matching the two components of the resulting $M@MXene$. The results obtained are in good agreement with analogous SAC studies on graphene⁴⁶ and graphynes.⁴⁷

In 2020, using the same approach, Co deposited on Mo_2CO_2 was used to investigate the CO oxidation by O_2 .⁴⁸ In agreement with previous results, it was shown that Co strongly bonds to a defective Mo_2CO_2 surface, and that CO adsorption is more favourable than O_2 adsorption. The relatively small activation energy barriers indicate that Eley–Rideal, Langmuir–Hinshelwood and termolecular Eley–Rideal mechanisms are all possible at low temperatures.

Unfortunately, no experimental studies on the CO oxidation reaction using MXene as the support were found in the literature, but we hope that the theoretical data presented in this review will pave the way for experimentalists to develop practical experiments in the near future. We emphasize here that before starting such experiments, the oxygen partial pressure in the system must be estimated and compared to that of the oxidation of the metal used. If the

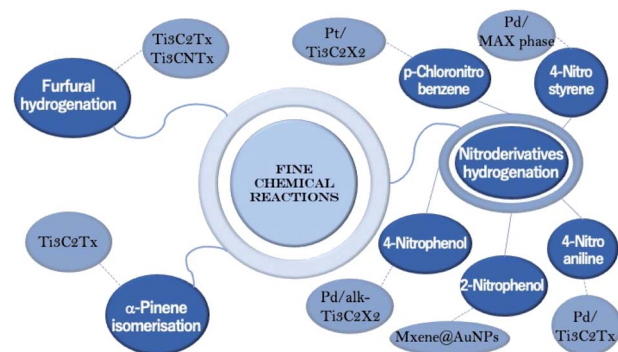

Scheme 3 Types of MAX phases and MXenes used in fine chemical reactions.

partial pressure is higher, they will oxidize which may or may not be useful.

The first experimental example involving CO activation on MXene is the water gas shift, WGS, reaction. In 2019, Deeva *et al.* demonstrated the stability of layered MXene structures based on Mo, in reducing environments when heated up to 550–600 °C. At higher temperatures (>730 °C), bulk $\beta-Mo_2C$ was evidenced.⁴⁹ To probe the catalytic properties, Mo_2CT_x was tested in the WGS reaction. In Fig. 7, its catalytic activity is compared with that of samples treated at 500 °C and reference $\beta-Mo_2C$. As expected, due to the surface functional groups, Mo_2CT_x showed a higher activity than the other catalysts. The highest activity was recorded at 520 °C with a peak consumption rate of CO of *ca.* 100 $\mu\text{mol}(\text{CO})\text{g}(\text{Mo})^{-1}\text{s}^{-1}$. Interestingly, this value is comparable to weight normalized rates of CO consumption obtained for the conventional Fe-based WGS catalyst, *i.e.*, Fe/Ce/Co oxide,⁵⁰ as well as for a 3.9 wt% Pt/ Al_2O_3 catalyst.⁵¹ At temperatures >700 °C, the activity of Mo_2CT_x diminished; however, the conversion values were still higher than those of other tested samples. It is important to note here that this Mo_2CT_x catalyst showed high stability in O-rich environments at high temperatures, as depicted in Fig. 7b and confirmed by XRD analysis, which shows that the tested Mo_2CT_x contained only trace amounts of MoO_2 .

These results represent the first proof demonstrating that Mo_2CT_x is a robust catalyst for high-temperature catalytic applications and that it is particularly stable against oxidation to MoO_2 .

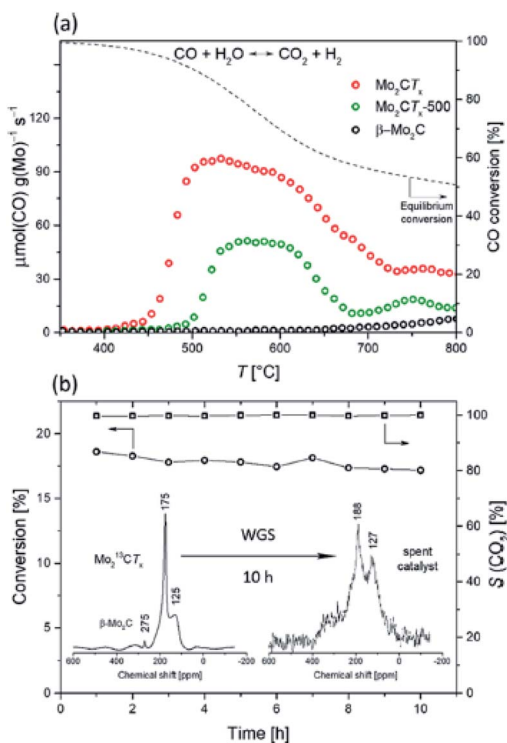


Fig. 7 (a) WGS catalytic activity of Mo_2CT_x , Mo_2CT_x -500, and $\beta-Mo_2C$ and (b) WGS stability test of Mo_2CT_x at 500 °C and ^{13}C MAS NMR (400 MHz, spinning rate 10 kHz) of $Mo_2^{13}CT_x$ before (1200 scans) and after (20 000 scans) the WGS catalytic test. Reprinted with permission from ref. 49 copyright 2019 American Chemical Society.

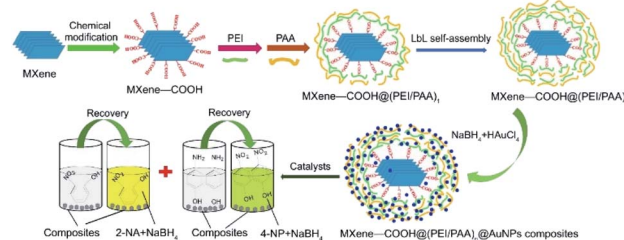


Fig. 8 Graphic design of synthesis and catalysis of $MXene-COOH@(PEI/PAA)_n@AuNP$ nanocomposites. Reproduced with permission from ref. 65, copyright 2018 Elsevier.

Table 1 Catalytic performance of MAX phases and MXene-based catalysts in hydrogenation reactions of nitro-compounds

Entry	Catalyst	Reactant	Conv. [%]	Selectivity [%]	Reaction time	Reducing agent	Ref.
1	MXene-COOH@(PEI/PAA) ₂ @AuNPs	2-Nitrophenol	70 (8 cycles)	—	60 min	—	65
2	MXene-COOH@(PEI/PAA) ₂ @AuNPs with fresh NaBH ₄	4-Nitrophenol	74 (8 cycles)	—	57 min		
3	MXene-COOH@(PEI/PAA) ₁₀ @AuNPs with fresh NaBH ₄	2-Nitrophenol	~90 (8 cycles)	—	36 min		
4	MXene-COOH@(PEI/PAA) ₁₀ @AuNPs with fresh NaBH ₄	4-Nitrophenol	~90 (8 cycles)	—	30 min		
5	Pd/alk-Ti ₃ C ₂ X ₂ in aqueous solution	4-Nitrophenol	99.9	100	70 min	H ₂	52
6	Pd/Ti ₃ C ₂ T _x C graphene hydrogels	4-Nitroaniline	91	—	1 min	NaBH ₄	69
7	Pd/Ti ₃ C ₂ T _x films on a poly(vinylidene fluoride) (PVDF) substrate	4-Nitroaniline	62.9	—	1 min		
8	Pd/Ti ₃ C ₂ T _x C graphene hydrogels	4-Chloronitrobenzene	~80	—	2 min		
			~98	—	5 min		
			~15	—	1 min		
9	Pd/Ti ₃ C ₂ T _x C graphene hydrogels	4-Bromonitrobenzene	~25	—	2 min		
			~45	—	5 min		
			~48	—	1 min		
10	Pd/Ti ₃ C ₂ T _x C graphene hydrogels	4-Nitrotoluene	~55	—	2 min		
			~60	—	5 min		
			~63	—	1 min		
11	Pd/Ti ₃ C ₂ T _x C graphene hydrogels	4-Nitrophenol	~72	—	2 min		
			~78	—	5 min		
			~70	—	1 min		
12	Ti ₃ SiC ₂	4-Nitrostyrene	~75	—	2 min		
			~79	—	5 min		
			<1	100	24 h	H ₂ 1.1 MPa	71
13	Ti ₂ AlC	4-Nitrostyrene	3	100		H ₂ 2.5 MPa	
			<1	100		H ₂ 1.1 MPa	
14	Ti ₃ AlC ₂	4-Nitrostyrene	1	100		H ₂ 2.5 MPa	
			<1	100		H ₂ 1.1 MPa	
15	0.05 wt% Pd/Ti ₃ SiC ₂	4-Nitrostyrene	4	13		H ₂ 2.5 MPa	
			100	0	24 h	H ₂	71
16	0.0005 wt% Pd/Ti ₃ SiC ₂	4-Nitrostyrene	100	0		H ₂	
17	0.0005 wt% Pd/Ti ₃ SiC ₂ -DP	4-Nitrostyrene	100	25		H ₂	
18	Pd/Ti ₃ SiC ₂ -mix1	4-Nitrostyrene	4	100		H ₂	
19	Pd/Ti ₃ SiC ₂ -mix2	4-Nitrostyrene	59 (cycle 1)	73		H ₂	
21	Pd/Ti ₃ SiC ₂ -mix3	4-Nitrostyrene	100 (cycle 2)	93		H ₂	
			100	58		H ₂	
22	Pd/Ti ₃ SiC ₂ -mix4	4-Nitrostyrene	100	10		H ₂	
23	Pd/TiC ₂ -mix2	4-Nitrostyrene	100 (cycle 1)	—		H ₂	
			18 (cycle 2)	—		H ₂	
25	Pd/Ti ₂ AlC ₂ -mix2	4-Nitrostyrene	52	27		H ₂	
26	Pd/Ti ₃ AlC ₂ -mix2	4-Nitrostyrene	100	—		H ₂	
27	Pd/Ti ₃ C ₂ T _x -mix2	4-Nitrostyrene	90 (cycle 1)	—		H ₂	
			25 (cycle 2)	—		H ₂	
29	Pd/Ti ₃ SiC ₂ -mix2	3-Nitrostyrene	100	96	24 h	H ₂	71
		Cinnamaldehyde	94	3 (cinnamyl alcohol) 80 (hydro-cinnamaldehyde)			
30	Ni/Ti ₃ SiC ₂	<i>Trans</i> -β nitrostyrene	9	13			
		4-Nitrophenol	18	83			
31	Pt/Ti ₃ C ₂ T _x -D-AB	4-Nitrostyrene	1	100	24 h	H ₂	71
		4-Chloronitrobenzene	100 ^a	99.5	1 h	H ₂	72
			94 ^a	92.4			
			99.8 ^a	95.2			
			96.9 ^a	92.9			
			2.6 ^a	67			
			98.2 ^b	95			
			78.1 ^c	90.8			
			39.3 ^d	83.3			

Table 1 (Contd.)

Entry	Catalyst	Reactant	Conv. [%]	Selectivity [%]	Reaction time	Reducing agent	Ref.
32	Pt/Ti ₃ C ₂ T _x -D-SB	4-Chloronitrobenzene	40.4 ^a	84.3			
33	Pt/Ti ₃ C ₂ T _x -D-AB	2-Chloronitrobenzene	100 ^a	96.5	1.5 h		
34	Pt/Ti ₃ C ₂ T _x -D-AB	3-Chloronitrobenzene	100 ^a	95.8	2 h		
35	Pt/Ti ₃ C ₂ T _x -D-AB	4-Nitrotoluene	100 ^a	98.2			
36	Pt/Ti ₃ C ₂ T _x -D-AB	2-Nitrotoluene	100 ^a	94.7			
37	Pt/Ti ₃ C ₂ T _x -D-AB	2-Methoxy-1-nitrobenzene	100 ^a	95.7	3 h		
38	Pt/Ti ₃ C ₂ T _x -D-AB	4-Nitrophenol	100 ^a	97.4	1.5 h		
39	Pt/Ti ₃ C ₂ T _x -D-AB	2-Fluoronitrobenzene	100 ^a	94.7			
40	Pt/Ti ₃ C ₂ T _x -D-AB	Nitrobenzene	100 ^a	99.2	1 h		

^a Reaction conditions: ethanol/water mixture with a volume percent of 28% (total volume: 7.0 mL); 14%; 42%; 56%; 100%. ^b Methanol/water mixture with a volume percent of 28% (total volume: 7.0 mL). ^c Propanol/water mixture with a volume percent of 28% (total volume: 7.0 mL).

^d 1,4-Dioxane/water mixture with a volume percent of 28% (total volume: 7.0 mL).

3. Fine chemical reactions

Fine chemical reactions are an important class of chemical transformations, in which MXenes are starting to be explored^{52–55} as catalysts due to their interesting properties (Scheme 3).

3.1. Isomerization of α -pinene

Recently, Zielińska *et al.*⁵⁶ tested Ti₃C₂T_x as a catalyst for the α -pinene isomerization reaction to camphene, one of the most pervasive monoterpenes. The target point of this catalytic process is to produce camphene with high selectivity because it is of great importance in the perfumery industry,⁵⁷ as an intermediate in organic synthesis. Lately, there have also been studies⁵⁸ confirming its anticancer properties.

The catalytic activity of Ti₃C₂ and exfoliated-Ti₃C₂ (ex-Ti₃C₂) was studied in α -pinene isomerisation and it was found that ex-Ti₃C₂ displays higher activity (60% conversion) than the unmodified Ti₃C₂ catalyst (48% conversion) and similar selectivity to camphene (~59 mol%).⁵⁶ There are many key factors that can explain the superior catalytic activity of ex-Ti₃C₂, particularly the higher specific surface area and the higher amount of acid sites of this catalyst.

Briefly, it was shown that ex-Ti₃C₂ shows much higher activity (100 mol% conversion of α -pinene in 7 h of process) compared with the multilayered Ti₃C₂. Moreover, the catalytic reactions were performed with smaller amounts of the catalyst and without solvent. The kinetic model was studied and the proposed pattern was well fitted to the experimental data for the isomerization of α -pinene; the reactions over both catalysts followed first-order kinetics. Additionally, the selectivity of the product of interest at 100% conversion is ~2 times higher for Ti₃C₂ MXenes compared with other Ti-based catalysts such as Ti-SBA-15 and Ti-MCM-41. Moreover, undesired dimerization and polymerization reactions were not detected.⁵⁶

3.2. Hydrogenation of nitroderivates

Catalytic hydrogenation reactions are among the most important reactions concerning the industrial production of chemicals.^{59,60}

Selective hydrogenation is difficult,⁶¹ especially when it is possible to hydrogenate more than one functional group per molecule of reactant.⁶² Heterogeneous metal-based catalysts possess chameleonic properties and are good materials to be developed for selective catalytic hydrogenation toward desired reaction products.⁶³ So, in the case of nitroderivates, the selective reduction of the –NO₂ groups while preserving intact the other reducible groups is highly desirable, but not easy. Typically, the nitrostyrene molecule, usually used as substrate, is considered to be the most demanding because the –C=C bond is quite sensitive and, consequently, more susceptible to be reduced than –NO₂.⁶⁴

Li *et al.*⁶⁵ reported the synthesis of functionalized core-shell MXene composites made by a layer-by-layer (LbL) self-assembly strategy *via* amine-containing polyethyleneimine (PEI) and carboxyl-containing polyacrylic acid (PAA), with the general formula MXene–COOH@(PEI/PAA)_n@AuNPs (see Fig. 8). The catalytic potential of the following two selected nanocomposites with different shell layers (*i.e.*, MXene–COOH@(PEI/PAA)₂@AuNPs and MXene–COOH@(PEI/PAA)₁₀@AuNPs) was investigated for catalytic reduction of 2-nitrophenol (2-NA) and 4-nitrophenol (4-NP). The composites revealed remarkable stability and repeatability (see Table 1, entries 1–4). Based on previous results reported a few years ago,⁶⁶ the obtained nanocomposite suspension was added to 2-NA or 4-NP with a fresh NaBH₄ mixture. After 8 consecutive cycles, the MXene–COOH@(PEI/PAA)₁₀@AuNPs showed enhanced stability and catalytic properties compared to their MXene–COOH@(PEI/PAA)₂@AuNP counterpart, with less LbL assembled shell structures, indicating the importance of LbL self-assembly for



Fig. 9 Schematic representation of the synthesis procedure of Pd/alk-Ti₃C₂T_x. Reproduced from ref. 52 (open access).

the improvement of porous structures and anchored sites on the surface.

Fan *et al.*⁵² used Pd/alk-Ti₃C₂T_x (alk = alkaline) as catalysts for the hydrogenation of 4-nitrophenol (4-NP) to 4-aminophenol (4-AP) in an aqueous solution.

The Pd/alk-Ti₃C₂T_x synthesis is described in Fig. 9, and the method used provides well dispersed active sites of Pd on the alk-Ti₃C₂T_x surface. This good dispersion in turn is responsible for the complete conversion and selective hydrogenation of 4-NP to 4-AP in 70 min. Additionally, the catalyst is stable showing no significant loss of catalytic efficiency after seven cycles, making it a promising candidate for numerous catalytic applications.

Noble metals such as Pd are intensively used in catalysis.^{67,68} Therefore, Xie *et al.*⁶⁹ described the synthesis of Pd/Ti₃C₂T_x encapsulated in 3D graphene networks, henceforth referred to as Pd/Ti₃C₂T_x⊂graphene hydrogels, as potent and easily retrievable catalysts for efficient hydrogenation of 4-nitroaniline (4-NA) to *p*-phenylenediamine (PPD) in the presence of NaBH₄

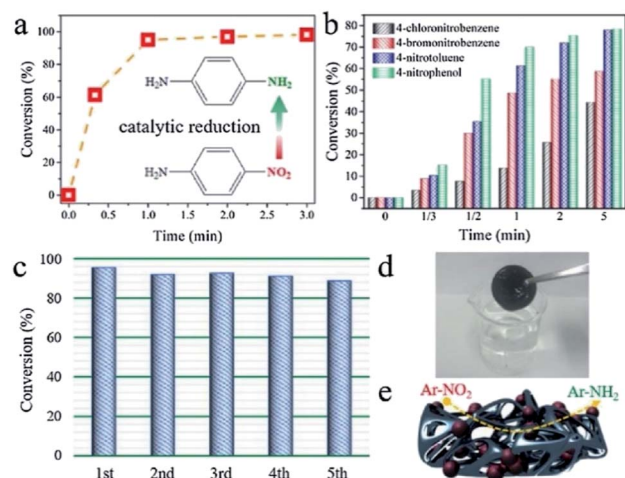


Fig. 10 Catalytic performance of the Pd/Ti₃C₂T_x⊂graphene hydrogel for (a) hydrogenation of 4-NA; (b) hydrogenation of other nitro-derivatives; (c) cycling performance for 4-NA dehydrogenation; (d) picture of the catalyst after the hydrogenation reaction; (e) schematic illustration of the catalytic dehydrogenation reaction. Reproduced with permission from ref. 69, copyright 2020 Elsevier.

as the reducing agent. The reaction is quite fast – 91% conversion after 1 min of reaction (see Fig. 10a) – demonstrating that the porous structure of the 3D Pd/Ti₃C₂T_x⊂graphene hydrogel is key for the accessibility of active sites for catalytic applications (see Table 1, entries 6–11).

Moreover, this hydrogel was tested for selective hydrogenation reactions with many other nitroaromatic molecules (*e.g.*, 4-chloronitrobenzene, 4-bromonitrobenzene, 4-nitrotoluene, and 4-nitrophenol) in order to prove the generality of this catalyst. The results (Fig. 10b) show that this catalyst results in exceptional catalytic performance with high conversion values for all these different nitro-compounds, mostly for those with electron donating functional groups (such as –CH₃ and –OH) compared to molecules with electron withdrawing substituents (*i.e.* –Cl and –Br) under the same reaction conditions.

Furthermore, it has been shown that the hydrogel is stable after successive recycle tests for the catalytic hydrogenation of 4-NA (see Fig. 10c).

To compare the results obtained with the Pd/Ti₃C₂T_x⊂*graphene hydrogel, Xie *et al.*⁶⁹ also prepared Pd/Ti₃C₂T_x films deposited on the poly(vinylidene fluoride) (PVDF) substrates. In this case, the conversion of 4-NA over the Pd/Ti₃C₂T_x catalyst was 63% after 1 min of reaction, which was much lower than the 91% obtained for the Pd/Ti₃C₂T_x⊂graphene hydrogel. The integrity of Pd/Ti₃C₂T_x films was preserved during the catalytic processes due to sodium ions and water intercalation into the Ti₃C₂T_x layers, also reported in other studies.⁷⁰

In a recent study, Trandafir *et al.*⁷¹ explored the use of MAX phases as supports for Pd nanoparticles (NPs), at remarkably low concentrations, for the chemoselective hydrogenation of a functionalized nitro-compounds.

The new generation of Pd NPs supported on the Ti₃SiC₂ catalyst used in the selective hydrogenation reaction of 4-NS achieved a high value of turnover frequency (TOF) of 4.7 × 10³ h⁻¹, that represents roughly a 100-fold increase over that of the most selective catalyst known to date (see Fig. 11a). 4-AS is the main product sought here, but other reaction products were identified (*i.e.*, 4-ethylnitrobenzene (4-EN) and 4-ethylaniline (4-EA)) depending on the reaction pathway (see Fig. 11b).

Different Pd supporting methods were explored (wet impregnation, deposition–precipitation, and mechanical mixing) and the authors found that the number of accessible sites appears to depend on the preparation method.

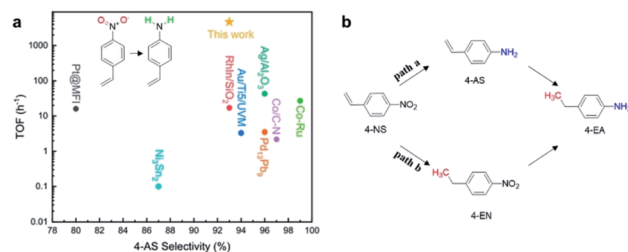


Fig. 11 (a) Comparison of the highest TOF values reported in the literature for catalysts in 4-NS hydrogenation to 4-AS, and (b) reaction pathways for the hydrogenation reaction of 4-NS. Reproduced with permission from ref. 71, copyright 2020 American Chemical Society.

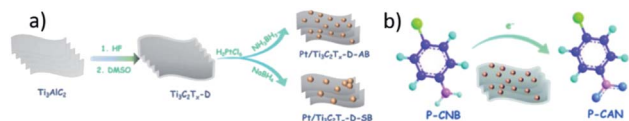


Fig. 12 (a) Schematic representation of the preparation process of Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D}$ samples with different reducing agents; (b) overview of the selective hydrogenation reaction of *p*-CNB to *p*-CAN with Pt–MXene based catalysts. Reproduced with permission from ref. 72, copyright 2020 Royal Society of Chemistry.

Actually, a good dispersion is obtained using a deposition–precipitation method compared with the large clusters formed through the impregnation method that consequently limited the access to the active sites. Diluting the Pd content by mechanically mixing the impregnated Pd samples with Ti_3SiC_2 was a good strategy to better control the Pd amount. A total conversion of 4-NS to 4-AS with a selectivity of 93% was obtained with an optimal loading of very well dispersed 130 ppm Pd. The authors also showed that higher Pd loadings resulted in selectivity losses. The high chemoselectivity of the Pd/MAX phase catalyst can be assigned to the synergetic effect between the Pd nanoparticle size and dispersion and also to the non-Ti containing oxides (*viz.* presence of SiO_2 as one of the native oxides formed in the Ti_3SiC_2 phase, the other being titania) that preferentially activate the nitro group. The proof of concept was realised by using the best material as the catalyst for different substrates (see Table 1 entries 12–30).

Additionally, Pt nanoparticles on $\text{Ti}_3\text{C}_2\text{T}_x$ -based MXenes as efficient catalysts have also been investigated recently⁷² for selective hydrogenation of *p*-chloronitrobenzene (*p*-CNB) to *p*-chloroaniline (*p*-CAN) (see Fig. 12b). Using ammonia borane (AB) as a mild reducing agent compared with sodium borohydride (SB), highly dispersed and nano-sized metallic Pt crystallites were uniformly decorated on $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets (see Fig. 12a). It was concluded that the reducing agent strongly influenced the particle size and distribution of the Pt NPs on the $\text{Ti}_3\text{C}_2\text{T}_x\text{-D}$ surface. It is remarkable that this catalyst can catalyse the complete conversion of *p*-CNB to *p*-CAN with 99.5% selectivity, and exhibits a superior catalytic activity to that of Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-SB}$ synthesized with SB (see Table 1, entries 31–32). The excellent performance of Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-AB}$ can be assigned to the well-dispersed Pt nanoparticles, abundant surface electron-efficient Pt(0) and also to the synergistic catalysis between hydrophilic Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-AB}$ and water (used as a co-solvent).

The Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-AB}$ catalyst was relatively stable for six cycles, after which it began to deactivate due to Pt aggregation as confirmed by TEM.

Chen *et al.*⁷² also tested Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-AB}$ in the hydrogenation of a series of nitroaromatic compounds to their corresponding amines with high efficiency (see Table 1, entries 33–40), with conversions that reached 100% in 1–3 h. The target products' selectivity is higher than 94% in all tests which indicates that Pt/ $\text{Ti}_3\text{C}_2\text{T}_x\text{-D-AB}$ is a flexible catalyst that can be used to obtain a series of aromatic amines.

3.3. Furfural hydrogenation

During the last decade, increased attention has been paid to selective biomass transformation. One of the most promising molecular platforms derived from hemicelluloses⁷³ is furfural, mainly considering the value added chemicals obtained by different catalytic reactions such as furfuryl alcohol.

Recently, Naguib *et al.*⁷⁴ reported the catalytic activity of $\text{Ti}_3\text{C}_2\text{T}_x$ and Ti_3CNT_x MXenes for the hydrogenation of furfural to furfuryl alcohol with the scope to understand the role of the presence of nitrogen in the support for carbonyl hydrogenation. Both catalysts had similar activities (36–42%) and selectivities (49–52%). It is worth mentioning that these results are similar or superior when compared with those of TiO_2 , metal carbides or other noble metal-free catalysts under the same conditions. The main difference between $\text{Ti}_3\text{C}_2\text{T}_x$ and Ti_3CNT_x was observed in terms of stability; Ti_3CNT_x was stable for six consecutive runs compared with $\text{Ti}_3\text{C}_2\text{T}_x$ which deactivated faster. This behaviour was explained by the differences of surface terminations, which varied as a function of MXene composition. $\text{Ti}_3\text{C}_2\text{T}_x$ is richer in surface terminations (especially OH), facilitating the intercalation of the reaction between the layers (leading to faster deactivation). The presence of nitrogen in Ti_3CNT_x significantly lowered the OH terminations and hindered the interaction of the surface with the reactants.

DFT calculations were performed to elucidate the furfural hydrogenation mechanism for Ti_3CNT_x . Apparently, TiO–H Brønsted acid sites present on the MXene surface bind to the furfural molecule by the C=O functional group, which is further hydrogenated *via* the addition of hydride dissociated on the metallic active site.


The bifunctionality of MXenes given by the presence of both metal and OH terminations which act as acids render these materials quite interesting for a wide range of catalytic reactions. Also, this study revealed that the surface terminations can have an influence on material stability, and suggests that MXene surfaces can be tuned in order to target certain reactions.

4. Catalytic degradation

4.1. Short overview

Pharmaceuticals and nonsteroidal anti-inflammatory drugs are used intensively for the treatment of human and animal diseases. The vast majority of drugs used end up in wastewater or groundwater, and removing or destroying them becomes a very difficult task due to their low or non-biodegradability.⁷⁵ Similar to pharmaceuticals, dyes also often end up polluting water systems and their removal is a subject of major interest. Dyes are used in many industries and the most common are methylene blue, rhodamine B, methyl orange or congo red.

Like dyes, pesticides can have a negative impact on humans and animals due to their toxic characteristics. For example, 2,4-dichlorophenoxyacetic acid was frequently found in drinking water in high concentrations due to its high solubility. The development of methods to remove this material from the environment is of great importance because its presence can

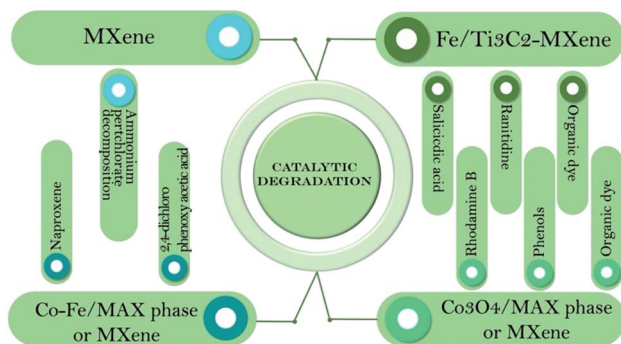

Scheme 4 Types of MAX phases and MXenes used in catalytic degradation reactions.

cause endocrinal disturbance and chromosomal mutations in human lymphocytes. It can also endanger aquatic life.⁷⁶

MAX phases and MXene-based heterojunction materials have been shown to be effective catalysts in the degradation of organic compounds such as pharmaceuticals,^{75,77,78} dyes,^{79,80} pesticides⁷⁶ and other compounds (see Scheme 4).^{81,82}

4.2. Ti_3C_2 -MXenes modified with iron compounds

Ding *et al.*⁷⁷ described the synthesis of a novel nanocomposite catalytic material obtained by supporting $\alpha\text{-Fe}_2\text{O}_3$ NPs onto multi-layered Ti_3C_2 and its use as a heterogeneous activator of peroxymonosulfate (PMS) for the degradation of salicylic acid. Salicylic acid is a phenolic compound widely used in the pharmaceutical, cosmetics and food industries. Due to the fact that it has been detected constantly in environmental water systems and that it represents a potential threat for ecological systems and humans, various methods to eliminate it from the aqueous environment have been developed. The authors claim that MXenes were selected for supporting $\alpha\text{-Fe}_2\text{O}_3$ nanoparticles because of the presence on their surface of different termination groups such as $-\text{O}$ and $-\text{OH}$, which provide better aqueous dispersibility and strong anchoring of the free cations through electrostatic interactions.⁷⁷

Three types of nanocomposites were synthesized, FM-1, FM-2, and FM-3, using different concentrations of $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ of 0.5 M, 1 M and 2 M, respectively. The $\alpha\text{-Fe}_2\text{O}_3/\text{MXene}$ nanocomposites present high efficiency and stability during the activation process of PMS to produce free radicals for the degradation of salicylic acid in aqueous solutions. Under neutral conditions, the removal of the salicylic acid was $\approx 97\%$ using the FM-2 catalyst nanocomposite. The catalytic system FM-2/PMS displayed low dissolution of metal ions and reusability during five successive runs. A possible mechanism of PMS activation was proposed by the authors based on EPR spectra, quenching tests, XPS and *in situ* Raman characterization.

Fig. 13 shows the mechanism which involves 4 steps. Salicylic acid is degraded by the reactive radicals generated during the PMS activation process. Unfortunately, the known instability of MXenes in water was not taken into account.

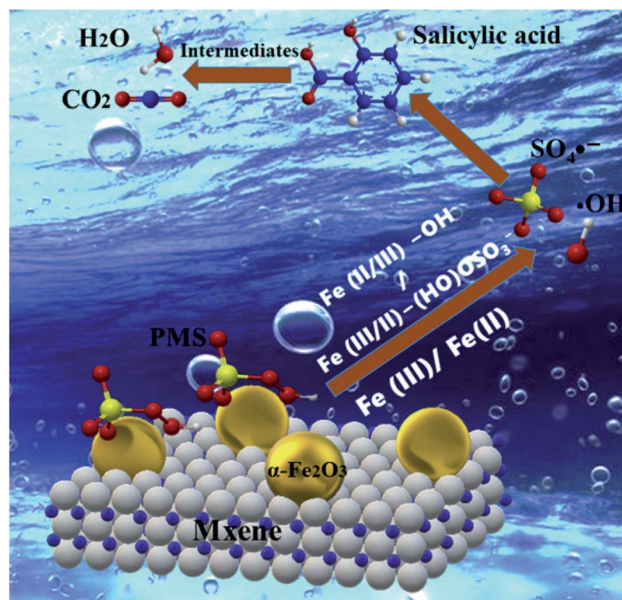


Fig. 13 Schematic diagram of the possible mechanism of PMS activation by FM nanocomposites. Reprinted with permission from ref. 77, copyright 2020 Elsevier.

Another example of drugs present in aquatic systems that require their removal from water is ranitidine, due to its carcinogenic effect. Ranitidine is frequently used as a histamine H_2 -receptor antagonist and is utilized for the treatment of ulcers and gastroesophageal reflux, due to the presence of furan rings in its structure.⁷⁸

Zang *et al.*⁷⁸ reported obtaining magnetic zero-valent iron ($n\text{ZVI}$)@ Ti_3C_2 -based MXene nanosheets *via* an *in situ* reductive deposition, which efficiently succeed in degrading ranitidine in the presence of H_2O_2 , a Fenton-like process (see Fig. 14). The proposed mechanism for catalytic degradation of ranitidine in the presence of H_2O_2 and ($n\text{ZVI}$)@ Ti_3C_2 -based MXene nanosheets (see Fig. 14) could be divided into five steps: (i) molecules of ranitidine diffuse and are adsorbed on the surface of the

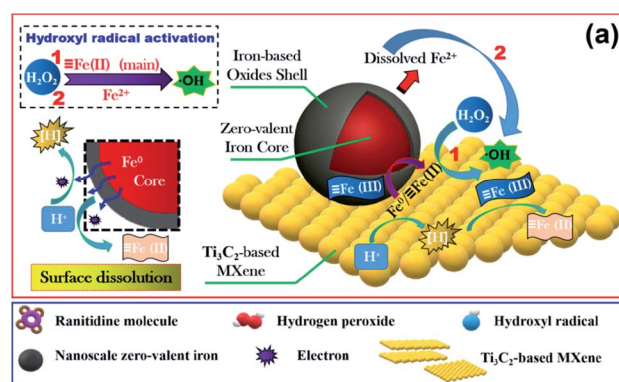


Fig. 14 Schematic of the mechanism of ranitidine catalytic degradation by the ($n\text{ZVI}$)@ $\text{Ti}_3\text{C}_2/\text{H}_2\text{O}_2$ system. Reprinted with permission from ref. 78, copyright 2021 Elsevier.

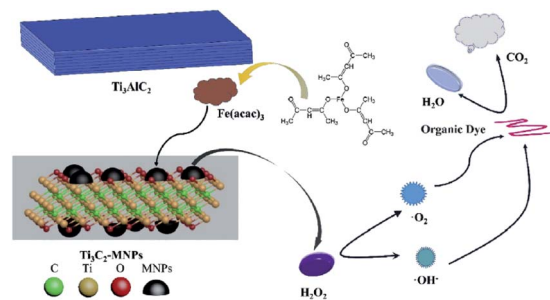


Fig. 15 Schematic of the synthesis of the $\text{Ti}_3\text{C}_2/\text{Fe}_3\text{O}_4$ system and its utilisation in dye degradation (reproduced with permission from ref. 80, copyright 2020 Elsevier).

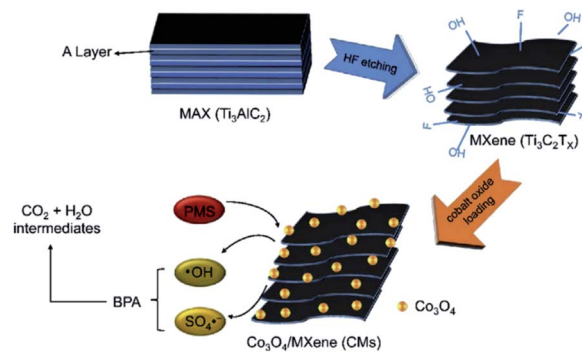


Fig. 17 Schematic of the synthesis of the $\text{Ti}_3\text{AlC}_2/\text{Co}_3\text{O}_4$ system and its utilisation in BPA catalytic degradation. Reprinted with permission from ref. 81, copyright 2018 Elsevier.

($n\text{ZVI}$)@ Ti_3C_2 nanosheets; (ii) the $n\text{ZVIs}$ undergo oxidative corrosion; (iii) cyclic transformation of $\equiv\text{Fe}(\text{iii})/\equiv\text{Fe}(\text{ii})$ occurs; (iv) ferrous iron activates H_2O_2 molecules; (v) hydroxyl radicals react with ranitidine. In this scheme the Ti_3C_2 -based MXene plays the role of a cathode, favouring a direct electron transfer reaction. The $n\text{ZVI}$ cores behave as an electron donor and the iron-based oxide outer shell promotes a series of $\equiv\text{Fe}(\text{iii})/\equiv\text{Fe}(\text{ii})$ conversions.

Apart from drug removal, a Fenton-like catalyst, $\text{Fe}_3\text{O}_4/\text{Ti}_3\text{C}_2$ -MXene proved to be efficient also in organic dye degradation. Zang *et al.*⁸⁰ developed, for the first time, a one-pot synthesis method for magnetic MXene composites (Ti_3C_2 -MNP) which incorporated Fe_3O_4 nanoparticles into Ti_3C_2 nanosheets *via* thermal treatment (see Fig. 15).

The hybrid $\text{Ti}_3\text{C}_2/\text{Fe}_3\text{O}_4$ system presents high degradation efficiency of organic dyes. The optimal conditions occur at $\text{pH} = 3$, a catalyst concentration and H_2O_2 concentration of 0.5 g L^{-1} and 10 mmol L^{-1} , respectively, and at a temperature = 40°C . The degradation mechanism involves the presence of hydroperoxyl radicals ($\text{OOH}\cdot$) and superoxide radicals ($\text{O}_2^{\cdot-}$).⁸⁰ Here again H_2O_2 is a very strong oxidizing agent and whether the MXene flakes would survive for times that are useful for an application has to be carefully considered.

4.3. MAX phases and MXenes modified with Co_3O_4

As in the case of Fe, Co also degraded organic dyes or phenols when it was deposited on MXenes and the MAX phases. Thus,

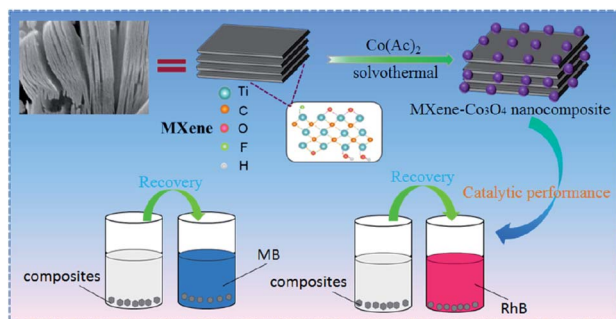


Fig. 16 Schematic representation of the synthesis of the $\text{Ti}_3\text{C}_2/\text{Co}_3\text{O}_4$ system and catalytic process of dye degradation. Reprinted with permission from ref. 79, copyright 2021 American Chemical Society.

nanocomposites of Co_3O_4 particle-modified MXene (MXene- Co_3O_4) synthesized by the solvothermal method showed good performance for catalytic degradation of methylene blue and rhodamine B (see Fig. 16).⁷⁹ The capacity of MXene- Co_3O_4 to degrade methylene blue and rhodamine B can be attributed to the positive synergistic effect of MXene, dye and Co_3O_4 in the presence of H_2O_2 . Cationic dye molecules were adsorbed on the MXene surfaces due to the electrostatic attraction and this process increased the concentration of dye molecules anchored on the surface of MXene- Co_3O_4 , leading to a high catalytic degradation rate. Also, the hydrophilicity of MXenes facilitated the dispersion of MXene- Co_3O_4 in water and improved the contact between molecules, and H_2O_2 was effectively catalyzed to produce free OH radical species that promoted dye degradation.⁷⁹

Wang *et al.*⁸¹ reported the synthesis of sandwiched $\text{Co}_3\text{O}_4/\text{Ti}_3\text{C}_2\text{T}_x$ composites as a heterogeneous catalyst to activate PMS for bisphenol A catalytic degradation, another toxic compound for humans and animals, released from polymers in the fabrication of water bottles, sport equipment, coatings of food containers, *etc.*⁸³ The $\text{Co}_3\text{O}_4/\text{Ti}_3\text{C}_2\text{T}_x$ composites were obtained by impregnation and the highest catalytic activity was obtained when the loading of Co_3O_4 was about 20% on $\text{Ti}_3\text{C}_2\text{T}_x$ (see Fig. 17). In addition, the $\text{Co}_3\text{O}_4/\text{Ti}_3\text{AlC}_2$ composite activates PMS for bisphenol A catalytic degradation, another toxic compound for humans and animals, released from polymers in the fabrication of water bottles, sport equipment, coatings of food containers, *etc.*⁸³ The $\text{Co}_3\text{O}_4/\text{Ti}_3\text{AlC}_2$ composite activates PMS for bisphenol A catalytic degradation, another toxic compound for humans and animals, released from polymers in the fabrication of water bottles, sport equipment, coatings of food containers, *etc.*⁸³ The $\text{Co}_3\text{O}_4/\text{Ti}_3\text{C}_2\text{T}_x/\text{PMS}$ system were $\text{SO}_4^{\cdot-}$ and $\text{OH}\cdot$ radicals.

4.4. MAX phases and MXenes modified with iron and cobalt

The high activity of Fe and Co supported on the MAX phases and MXenes observed in catalytic degradation encouraged the researchers to also continue and explore the synergy between the two elements (Fe and Co). Fayyaz *et al.*⁷⁵ described the synthesis of a heterogeneous nanocomposite catalyst of MXene nanosheets (synthesized from Ti_3AlC_2) functionalized with CoFe_2O_4 nanoparticles that can be used for the activation of persulfate (PS) to degrade naproxen in water. Naproxen is a nonsteroidal anti-inflammatory drug used in the treatment of rheumatoid arthritis and acute muscle pain⁷⁵ and is similar to

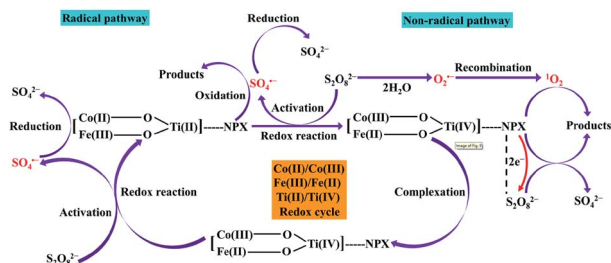


Fig. 18 Proposed mechanism for naproxen degradation with PS activated by CoFe_2O_4 @MXene. Reprinted with permission from ref. 75, copyright 2021 Elsevier.

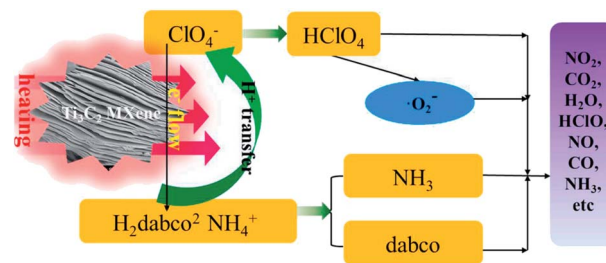


Fig. 19 Schematic of the catalysis decomposition mechanism of $[(\text{H}_2\text{dabco})[\text{NH}_4(\text{ClO}_4)_3]$ with Ti_3C_2 MXene. Reprinted with permission from ref. 82, copyright 2020 Elsevier.

salicylic acid; it contaminates environmental water systems and its removal is a subject of major interest.

The experiments described by the authors confirm that neither CoFe_2O_4 nanoparticles nor MXenes alone can activate PS, but the CoFe_2O_4 @MXene system proved to be an efficient catalyst for PS activation. A proposed mechanism for naproxen degradation with persulfate activated by this nanohybrid system is described in Fig. 18.

Coordination interactions of Co and Fe moieties with MXene functional groups modulate redox reactions of stable Co/Fe/Ti couples. The electrons are transferred from PS to form $\text{SO}_4^{\cdot-}/\text{S}_2\text{O}_8^{\cdot-}$ by thermodynamic oxidation of Co(II)/Fe(II)/Ti(II) and reduction of Co(III)/Fe(III)/Ti(IV). By activating PS with the CoFe_2O_4 @MXene, radical reactive species such as $\cdot\text{OH}$, $\text{SO}_4^{\cdot-}$, and $\text{O}_2^{\cdot-}$ and the corresponding nonradical $^1\text{O}_2$ are formed, which significantly promotes naproxen degradation.

Moreover, the naproxen adsorbed on the CoFe_2O_4 @MXene acts as an electron donor and transfers two electrons to PS that is, in turn, reduced to 2SO_4^{2-} . Naproxen was degraded approximately 99% in the presence of PS at 1 g L^{-1} of CoFe_2O_4 @MXene dosage.

Composites such as $\text{Fe}_2\text{CoTi}_3\text{O}_{10}$ -MXene were described by Ding *et al.*⁷⁶ as a heterogeneous catalyst for oxidative degradation of 2,4-dichlorophenoxyacetic acid based on PMS activation. These composites could efficiently activate PMS and, under neutral conditions, approximately 98% of 2,4-dichlorophenoxyacetic acid was removed. In the catalytic oxidation process, radicals such as $\cdot\text{OH}$ and $\text{SO}_4^{\cdot-}$ are generated and the main activation mechanism for PMS can be represented by the electron transfer between PMS and ternary transition metal (Fe, Co and Ti) active sites on the catalyst surface.⁷⁶

It is our duty to inform the readers that the catalytic degradations presented in Sections 4.1–4.4, that use Ti-based MXenes, are useful from the academic/fundamental point of view, showing some synergetic effects between the supported Fe and Co transition metals and the Ti-based MXenes. Unfortunately, Ti-based MXenes are not stable in water for a long time, and therefore any practical applications are not feasible.

In addition, when studying the Fenton degradation of drugs in aquatic systems, researchers should take into account that the use of H_2O_2 will also result in faster oxidation of MXenes and their transformation into metal oxides will occur.

4.5. MXenes for ammonium perchlorate decomposition

Recently, Jiao *et al.*⁸² showed that Ti_3C_2 has intrinsic catalytic activity for the thermal decomposition of ammonium perchlorate-based molecular perovskites such as $[(\text{H}_2\text{dabco})[\text{NH}_4(\text{ClO}_4)_3]$. Experiments revealed that adding 10 wt% Ti_3C_2 to the reaction mixture reduced the decomposition temperature by $43.8 \text{ }^\circ\text{C}$ at a heating rate of $10 \text{ }^\circ\text{C min}^{-1}$.

The catalytic mechanism (Fig. 19) proposed by the authors assumed that the thermal decomposition of ammonium perchlorate-based molecular perovskites is mainly determined by the stability of the cage-like framework structures of the substrate which were composed of NH_4^+ cations and ClO_4^- anions.⁸²

The inherent catalytic properties of MXenes can realise the thermal decomposition of ammonium perchlorate-based molecular perovskites by lowering the decomposition temperature and activation energy, and increasing the heat release.⁸²

Along the same lines, Cu_2O supported on Ti_3C_2 MXenes was found to provide a higher catalytic activity compared with Ti_3C_2 MXenes or Cu_2O alone, in the thermal decomposition of ammonium perchlorate (AP).⁸⁴ Combining the advantages of Cu_2O and MXenes, good thermal conductivity, improved heat transfer rate of the reaction system and also high surface area and lamellar structure of MXenes, the thermal decomposition temperature of ammonium perchlorate was significantly reduced by $121.4 \text{ }^\circ\text{C}$ compared to that of the pure AP.

In 2021, Li *et al.*⁸⁵ demonstrated that Ti_3C_2 MXene-supported CuO nanocomposites also significantly decrease the decomposition temperature of AP from $425.0 \text{ }^\circ\text{C}$ to $324.9 \text{ }^\circ\text{C}$ and increase the exothermic heat from 295.2 J g^{-1} of AP to 1272.9 J g^{-1} .

These results prove that the MXene used as a support for CuO or Cu_2O could be a viable solution to enhance the catalytic performance in ammonium perchlorate decomposition, which is of major interest.

5. Applications of MXenes in photocatalysis

5.1. Short overview

Photocatalysis can be described as the acceleration of a photo-reaction in the presence of a catalyst, called a photocatalyst, that

Table 2 Comparison of $\text{Ti}_3\text{C}_2\text{T}_x$ MXene photocatalysts in the hydrogen evolution reaction^a

Photocatalyst	Preparation methods	Reaction conditions	Light source	Sacrificial reagent	H_2 production [$\mu\text{mol g}^{-1} \text{h}^{-1}$]	AQY [%]	Ref.
Pt/ZnIn ₂ S ₄ /Ti ₃ C ₂ T _x (3 wt% Pt)	Solvothermal procedure	20 mg catalyst dispersed in 40 mL TEOA (10 v%)	300 W Xe lamp ($\lambda \geq 400$ or 420 nm)	TEOA	6482 (≥ 400 nm)	20.41 (400 nm)	105
Chlorophyll-Ti ₃ C ₂ T _x	Electrostatic self-assembly process	3 mg catalyst dispersed in 3 mL AA (55 mM)	350 W Xe lamp ($\lambda \geq 400$ nm)	AA	3475 (≥ 420 nm)	11.14 (420 nm)	106
MXene@Au@CdS	Stepwise approach	4 mg catalyst dispersed in 80 mL sacrificial agent aqueous solution	300 W Xe lamp ($\lambda \geq 420$ nm)	0.25 M Na ₂ SO ₃ and 0.35 M Na ₂ S	17 070.43	np	107
TiO ₂ -Ti ₃ C ₂ /Ru	Stepwise approach	10 mg catalyst dispersed in 80 mL methanol (10 v%)	300 W Xe lamp (350–780 nm)	Methanol	235.3	14.33 (350 nm)	108
P-g-C ₃ N ₄ /Ti ₃ C ₂ T _x	Electrostatic self-assembly process	40 mg catalyst dispersed in 60 mL TEOA (10 v%)	300 W Xe lamp	TEOA	982.8	np	109
CdL _{0.2} S _{0.8} /Ti ₃ C ₂	Hydrothermal procedure	50 mg catalyst dispersed in 100 mL sacrificial agent aqueous solution	300 W Xe lamp ($\lambda \geq 420$ nm)	0.25 M Na ₂ SO ₃ and 0.35 M Na ₂ S	11 182.4	15.6 (420 nm)	110
BIVO ₄ @ZnIn ₂ S ₄ /Ti ₃ C ₂	Ultrasonic assisted self-assembly process	60 mg catalyst	300 W Xe lamp ($\lambda \geq 420$ nm)	No scavenger	102.67	2.9 (460 nm)	111
g-C ₃ N ₄ /Ti ₃ C ₂	Stepwise approach	50 mg catalyst dispersed in 100 mL TEOA (10 v%)	300 W Xe lamp ($\lambda \geq 420$ nm)	TEOA	116.2	np	112
CdS@Ti ₃ C ₂ @CoO	Stepwise approach	20 mg catalyst dispersed in 100 mL DI	300 W Xe lamp ($\lambda \geq 420$ nm)	No scavenger	134.46	np	113
2 wt% Pt/UCN/Ti ₃ C ₂ T _x /BQD	Stepwise approach	10 mg catalyst dispersed in 78 mL TEOA (10 v%)	300 W Xe lamp ($\lambda \geq 420$ nm)	TEOA	18 420	17.6 (420 nm)	101
Cd _{0.5} Zn _{0.5} S/Ti ₃ C ₂	Hydrothermal procedure	50 mg catalyst dispersed in 100 mL DI or seawater	300 W Xe lamp ($\lambda \geq 420$ nm)	0.25 M Na ₂ SO ₃ and 0.35 M Na ₂ S	9.07	43.28 (420 nm, DI splitting and AM 1.5G)	114
1 wt% Pt/HCN/Ti ₃ C ₂	Isonothermal method	20 mg catalyst dispersed in 100 mL TEOA (10 v%)	3 W LED lamp (420 nm)	TEOA	4225	14.6 (420 nm)	115
CdS nanorods/Ti ₂ C ₃ T _x	Hydrothermal procedure	20 mg catalyst dispersed in 100 mL TEOA (20 v%)	300 W Xe lamp	TEOA	63.53	2.28	116
TiO ₂ -C/CdS synthesized from Ti ₃ C ₂ /CdS	Calcination	50 mg catalyst dispersed in 100 mL lactic acid (20 v%)	300 W Xe lamp ($\lambda \geq 420$ nm)	Lactic acid	1480	np	102
0.5 wt% Pt/TiO ₂ @C synthesized from Ti ₃ C ₂	Calcination	35 mg catalyst dispersed in 100 mL TEOA (10 v%)	Solar simulator AM 1.5G	TEOA	160.42	np	103


^a Results included in studies published starting from 2020 onwards only; AA: ascorbic acid; UCN: ultrathin carbon nitride; BQD: black phosphorus quantum dots; TEOA: triethanolamine; DI: deionized water; HCN: heptazine-based crystalline carbon nitride; np: information not provided by authors.

is often stable to the photolysis conditions and attains a large number of oxidative conversions per active site without significant degradation of its redox catalytic capacity.⁸⁶ In the case of heterogeneous photocatalysis, upon photoexcitation of several semiconductor photocatalysts nonhomogeneously suspended in either aqueous or nonaqueous solutions or in gaseous mixtures, the photogenerated electron-hole pairs migrate to the external surface and initiate simultaneous oxidation and reduction reactions.^{86,87} Depending on the reaction media, the photogenerated electrons and holes might interact directly with the adsorbate molecules (*e.g.*, the photocatalytic overall water splitting reaction) or create reactive species (*e.g.*, hydroxyl and superoxide radicals) that undergo non-selective oxidative processes to break down different substances including organic materials, pesticides, dyes or bacteria, among others.⁸⁸

The major hurdle that needs to be overcome in this area is the recombination of photogenerated electrons and holes. In this regard, the combination of MXenes with various semiconductor photocatalysts led to a marked increase in photoactivity. Such phenomena are caused by the structural merits of MXenes including (i) abundant hydrophilic groups ($-OH$ and $-O$) present on the external surfaces that afford considerable interaction with various semiconductors to form composite heterostructured photocatalysts, (ii) strong redox activities of surface metal sites (*e.g.*, Ti, Nb or V) existing on the MXene surfaces which are greater than the redox reactivity of carbon materials,⁸⁹ and (iii) due to their metallic character, MXenes possess excellent electron conductivity that guarantees efficient charge transport.⁹⁰

As a typical representative of MXene materials, $Ti_3C_2T_x$ features high electrical conductivity, surface hydrophilicity, and tuneable electronic properties that makes it a suitable co-catalyst in various photocatalytic applications. Thus, benefitting from the Schottky effect (due to the high work functions of $Ti_3C_2T_x$ 3.9–4.8 eV depending on the surface termination in comparison with those of most well-established semiconductor photocatalysts)⁹¹ and the accompanying built-in electric field, the photogenerated charges of several semiconductors interfaced with $Ti_3C_2T_x$ can be effectively separated and, from a photocatalytic point of view, this process enhances the activity of the photocatalytic system.

Due to their excellent metallic conductivity (the measured conductivity of single-layer $Ti_3C_2T_x$ was reported to be up to $6.76 \times 10^5 \text{ S m}^{-1}$, which is comparable to that of graphene films that is situated in the range of 5×10^6 to $6.4 \times 10^6 \text{ S m}^{-1}$),^{92,93} MXenes can boost the activity of semiconductor photocatalysts. In comparison with graphene, however, the use of MXenes as co-catalysts brings several advantages.^{94,95} For instance, in the construction of graphene-based semiconductor photocatalysts, the majority of the literature data report the use of graphene oxide (GO), followed by a reduction process to generate reduced graphene oxide (RGO).⁹⁶ The adoption of this synthesis route causes a significant loss in electronic conductivity due to the presence of numerous point defects, and the reported electrical conductivity of RGO ($<1 \times 10^3 \text{ S m}^{-1}$)⁹⁷ is about two orders of magnitude below the conductivity of $Ti_3C_2T_x$. Another interesting discovery shows that MXenes can serve as hole acceptors

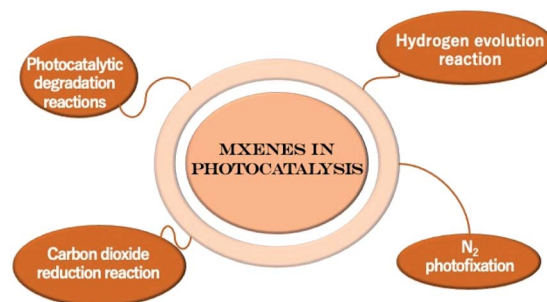

Scheme 5 MXenes in photocatalysis.

during the photocatalytic reactions, a fact that was never reported in the case of graphene-based semiconductor photocatalysts.⁹⁴

On the other hand, use of $Ti_3C_2T_x$ as a co-catalyst comes with a big disadvantage: its low stability in water. However, within the formed photocatalytic composite, $Ti_3C_2T_x$ should not be seen as the Trojan horse, since the oxidized product is TiO_2 , which itself possesses excellent photoactivity. Moreover, as will be shown later in Tables 2–4, the stability and the photoactivity of the photocatalyst composite obtained by the *in situ* approach (*e.g.*, solvothermal procedure) are significantly greater than those obtained by the electrostatic self-assembly process.

The application of $Ti_3C_2T_x$ in the field of photocatalysis is summarized in this review by the following four aspects: (i) the photocatalytic hydrogen, H_2 , evolution reaction (HER) through water splitting, (ii) photocatalytic carbon dioxide, CO_2 , reduction reaction (CO_2RR), (iii) photocatalytic degradation reactions of various pollutants, and (iv) nitrogen photofixation and other photocatalytic/photo-assisted processes (see Scheme 5). As many reviews were recently published on this topic,^{11–14} here we only report the studies published in 2020–2021. Moreover, the aim of this section is not to provide an exhaustive review of this area, but to present general aspects to be considered, and then to outline which are currently the most efficient photocatalytic systems comprising $Ti_3C_2T_x$.

5.2. Applications in the hydrogen evolution reaction

As stated above, after photogeneration, the electron-hole pairs initiate simultaneous oxidation and reduction reactions on the outer surfaces of the photocatalyst. In order to maintain charge neutrality during the photocatalytic process, the consumption rate of electrons and holes must be equal. For this reason, most of the studies on the HER are carried out with an excess of electron donor reagents.⁹⁸ Thus, while the holes are quenched and used by different hole scavengers, the electrons reduce the H^+ species, followed by the formation of intermediate adsorbed H^* states and finally the production of H_2 molecules.⁹⁹

In the field of H_2 generation through photocatalytic water splitting, the first synthesized MXene, $Ti_3C_2T_x$, is also the most widely used because it forms Schottky junctions that promote the separation of photogenerated charge carriers. Besides this, the DFT calculated Gibbs free energy for atomic H adsorption on the surface of O-terminated Ti_3C_2 ($|\Delta G_{H^*}| = 0.00283 \text{ eV}$)⁸⁹ is

much lower than that of the highly active and well-known HER catalyst, Pt ($\Delta G_{H^*} \approx -0.09$ eV)¹⁰⁰ and thus much closer to the most desired $|\Delta G_{H^*}|$ value which should be zero.⁹⁹

Table 2 summarizes several examples of $Ti_3C_2T_x$ -based photocatalysts used in the most recent years for the HER. The synthetic approaches to combine different semiconductor photocatalysts with $Ti_3C_2T_x$ and several reaction parameters are also presented. These reports demonstrated that $Ti_3C_2T_x$ could greatly improve the photoactivity compared to solely the base photocatalyst. The highest H_2 production activity and apparent quantum efficiency (AQE) of 18.42 mmol $h^{-1} g^{-1}$ and 17.6% (at 420 nm), respectively, were obtained when Ti_3C_2 nanosheets were mixed with ultrathin 0D/2D black phosphorus/ultrathin carbon nitride heterojunctions that were loaded with 2 wt% Pt and tested in photocatalytic water splitting in the presence of triethanolamine as a hole scavenger.¹⁰¹

Besides its role as a co-catalyst, $Ti_3C_2T_x$ can be used as a precursor for the generation of TiO_2 -based active photocatalysts through a simple thermal degradation process.^{102,103} Thus, flash oxidation of 2D $Ti_3C_2T_x$ in air resulted in the formation of a hybrid structure of thin sheets of disordered graphitic carbon decorated with nanocrystalline anatase.¹⁰⁴ In this regard, Table 2 presents two of the most recent experiments comprising the use of $Ti_3C_2T_x$ as a precursor for obtaining photocatalysts with remarkable photoactivity toward the HER (see ref. 92 and 93).

5.3. Applications in the carbon dioxide reduction reaction, CO_2RR

In comparison with photocatalytic water splitting, the photocatalytic reduction of CO_2 is a much more complicated process, due to several aspects which include but are not limited to the following: (i) although water is the most suitable hydrogen donor for CO_2 reduction, in aqueous solutions, the HER competes with the CO_2RR ; (ii) while basic pH increases CO_2 solubility in water, this is not necessarily advantageous since, under these conditions, the real species that are present would be carbonates or bicarbonates, which are more difficult to reduce than CO_2 itself and, in this way, the advantages of high

solubility, meaning the high concentration of the substrate around the photocatalyst is lost; (iii) performing the CO_2RR under gas phase conditions might lead to the formation of less volatile reaction products that can strongly adsorb or deposit on the photocatalyst surface and act as poisons; (iv) in cases in which the concentration of the CO_2RR products is low, the impurities (e.g., adsorbed airborne organic compounds) present on the surface of the photocatalyst might lead to misleading results concerning the real activity of the photocatalysts.¹¹⁷

Considering all these difficulties, it is not surprising that the number of studies on the CO_2RR are much less than those on water splitting. More importantly, the instability of the MXene carbon atoms causing interference during the CO_2RR limits the application of $Ti_3C_2T_x$ -based photocatalysts in the CO_2RR in comparison with its use for photocatalytic water splitting.

As shown in Table 3, among the limited reports in recent years, $Ti_3C_2T_x$, as a co-catalyst, promotes the separation of charge carriers, leading to the formation of solely C1 products (i.e., CO and CH_4), while the lack of the formation of C2 products (e.g., formaldehyde, formic acid or oxalic acid) indicates that $Ti_3C_2T_x$ cannot change the energy barrier of the base photocatalyst.

A great enhancement of the photoactivity toward the CO_2RR was obtained by Que *et al.*¹¹⁸ by anchoring inorganic halide perovskite $FAPbBr_3$ (formamidinium lead bromide) quantum dots on Ti_3C_2 nanosheets to form a $FAPbBr_3/Ti_3C_2$ composite with a Schottky heterojunction. Thus, under visible light irradiation, an optimal electron consumption rate of 717 $\mu mol g^{-1} h^{-1}$ is obtained, which corresponds to a ≈ 2 -fold improvement over that of pristine $FAPbBr_3$ QDs (344 $\mu mol g^{-1} h^{-1}$).

5.4. Applications in photocatalytic degradation reactions

Degradation of both atmospheric and aquatic organic contaminants can be efficiently performed through heterogeneous photocatalysis. Here the photocatalytic degradation process follows three main steps: (i) photogeneration of electron-hole pairs upon light irradiation, (ii) formation of highly active radicals (i.e., $\cdot OH$, $O_2^{\cdot -}$, and $HOO\cdot$) on the surface as

Table 3 Comparison of $Ti_3C_2T_x$ MXene photocatalysts in the carbon dioxide reduction reaction^a

Photocatalyst	Preparation methods	Reaction conditions	Light source	Products and yield [$\mu mol g^{-1} h^{-1}$]	Ref.
$FAPbBr_3/Ti_3C_2$	Deposition	3 mg catalyst, 0.5 mL deionized water and CO_2 (1 bar)	300 W Xe lamp ($\lambda \geq 420$ nm)	283.41 (CO) 17.7 (CH_4)	118
$Cu_2O/Ti_3C_2T_x$	Hydrothermal procedure	30 mg catalyst coated onto a quartz plate and CO_2 (<1 atm)	300 W Xe lamp	17.5 (CO) 1.0 (CH_4)	119
$g-C_3N_4/Ti_3C_2T_x$	Calcination	50 mg catalyst uniformly dispersed on a 28.26 cm^2 glass sheet, 5 mL water and 1 mL CO_2 gas	300 W Xe lamp	2.1 (CH_4) 4 (CO)	120
$g-C_3N_4/TiO_2/C$ synthesized from $Ti_3C_2T_x$	Electrostatic self-assembly and calcination	Certain amounts of catalyst and water and CO_2 (ca. 1 atm)	Arc Xe lamp	8.65 (CO) 1.23 (CH_4)	121

^a Results included in studies published starting from 2020 onwards only.

Table 4 Comparison of $\text{Ti}_3\text{C}_2\text{T}_x$ MXene photocatalysts in photocatalytic degradation reactions^a

Photocatalyst	Preparation methods	Reaction conditions	Light source	Substrate of degradation	Oxygenic species	Removal rate/rate constants [%]/[min^{-1}]	Ref.
$\text{ZnO-Ti}_3\text{C}_2$	Ultrasonic assisted self-assembly process	35 mg catalyst dispersed in 50 mL RhB (10 mg L^{-1})	300 W Xe lamp ($\lambda \geq 420$ nm)	RhB	np	98/0.0077	133
$\text{Bi}_2\text{WO}_6/\text{C}_3\text{N}_4/\text{Ti}_3\text{C}_2$	Hydrothermal procedure	30 mg catalyst dispersed in 200 mL CIP (10 mg L^{-1})	300 W Xe lamp	CIP	$\text{h}^+/\text{O}_2^{\cdot-}$	0.058	134
$\text{TiO}_2(\text{TiO}_{2-x})/\text{Ti}_3\text{C}_2$	Stepwise synthesis	5 mg catalyst dispersed in 50 mL BPA (15 mg L^{-1})	300 W Hg lamp ($\lambda < 365$ nm)	BPA	$\cdot\text{OH}/\text{O}_2^{\cdot-}$	90.5	135
$\text{Ti}_3\text{C}_2/\text{Ti}^{3+}-\text{TiO}_2$	Stepwise synthesis	100 mg catalyst coated on a glass slide. Continuous flow (20 sccm) of acetaldehyde (500 ppm)	500 W Xe lamp ($\lambda \geq 420$ nm)	Acetaldehyde	$\cdot\text{OH}/\text{O}_2^{\cdot-}$	27	136
$\alpha\text{-Fe}_2\text{O}_3/\text{ZnFe}_2\text{O}_4@/\text{Ti}_3\text{C}_2$	Ultrasonic assisted self-assembly process	20 mg catalyst dispersed in 100 mL RhB (10 mg L^{-1}) or Cr(vi) (10 mg L^{-1})	300 W Xe lamp ($\lambda \geq 400$ nm)	RhB Cr(vi)	$\text{O}_2^{\cdot-}/\text{h}^+/\text{e}^-$	$\sim 98/0.02686$	137
$\text{Ti}_3\text{C}_2/\text{TiO}_2$	Solvothermal procedure	20 mg catalyst dispersed in 50 mL RhB (20 mg L^{-1})	300 W Xe lamp	RhB	h^+	93.7	138
$\text{TiO}_2/\text{g-C}_3\text{N}_4$ synthesized from Ti_3C_2	Calcination	60 mg catalyst dispersed in 100 mL of pollutants	300 W Xe lamp ($\lambda \geq 400$ nm)	TC CIP BPA RhB	$\text{O}_2^{\cdot-}/\cdot\text{OH}$	0.02442 0.01675 0.01935 0.05586	139
$\text{BiOBr}/\text{TiO}_2/\text{Ti}_3\text{C}_2\text{T}_x$	Hydrothermal procedure	20 mg catalyst dispersed in 50 mL RhB	300 W Xe lamp ($\lambda \geq 420$ nm)	RhB	$\cdot\text{OH}/\text{O}_2^{\cdot-}$	99.8	140
$\text{Ti}_3\text{C}_2/\text{TiO}_2/\text{BiOCl}$	Solvothermal procedure	50 mg catalyst dispersed in 50 mL RhB (10 mg L^{-1}) or TC (20 mg L^{-1})	500 W Xe lamp AM 1.5G	RhB TC	$\text{O}_2^{\cdot-}/\cdot\text{OH}$	84/0.0143 0.0157	141
$\text{TiO}_2/\text{Ti}_3\text{C}_2\text{T}_x$	Solvothermal procedure	Certain amount of catalyst dispersed in 100 mL MO	500 W Hg lamp	MO	Np	92	142
$\text{Ti}_3\text{C}_2/\text{BiPO}_4$	Hydrothermal procedure	100 mg catalyst dispersed in 50 mL RhB (10 mg L^{-1})	300 W Xe lamp ($\lambda \geq 420$ nm)	RhB	$\text{O}_2^{\cdot-}/\cdot\text{OH}$	100/0.12469	143
$\text{ZnO}/\text{Ti}_3\text{C}_2$	Hydrothermal procedure	50 mg catalyst dispersed in 200 mL MB (10 mg L^{-1})	40 W Hg lamp (365 nm)	MB	$\text{O}_2^{\cdot-}/\cdot\text{OH}$	83.97/0.03357	144
$\text{Ti}_3\text{C}_2/\text{TiO}_2$	Hydrothermal oxidation method	Certain amount of catalyst (200 mg L^{-1}) and PFOA (20 μM)	Hg lamp (254 nm)	PFOA	Np	99.9	145
$\text{CoAl-LDHs}/\text{Ti}_3\text{C}_2\text{T}_x$	Electrostatic self-assembly process	100 mg catalyst dispersed in 100 mL TCH	300 W Xe lamp ($\lambda \geq 420$ nm)	TCH	$\text{O}_2^{\cdot-} > \text{h}^+ > \cdot\text{OH}$	96.67	146
$\text{Ag}/\text{Ag}_3\text{PO}_4/\text{Ti}_3\text{C}_2$	Electrostatic self-assembly process	50 mg catalyst dispersed in 100 mL MO (20 mg L^{-1})	300 W Xe lamp ($\lambda \geq 420$ nm)	MO	h^+, e^-	93/0.044	147
		40 mg catalyst dispersed in 80 mL Cr(vi) (10 mg L^{-1})		Cr(vi)	h^+, e^-	61/0.014	

Table 4 (Contd.)

Photocatalyst	Preparation methods	Reaction conditions	Light source	Substrate of degradation	Oxygenic species	Removal rate/rate constants [%]/[min ⁻¹]	Ref.
TiO ₂ /Ti ₃ C ₂	Stepwise synthesis	40 mg catalyst dispersed in 50 mL RhB (20 μM)	Solar simulator AM 1.5G	RhB	$\cdot\text{OH} > \text{O}_2^{\cdot-}$	95	148
CaIn ₂ S ₄ /Ti ₃ C ₂ T _x	Hydrothermal procedure	50 mg catalyst dispersed in 50 mL TCH (20 mg L ⁻¹) or Cr(vi) (20 mg L ⁻¹)	400 W metal halogen lamp (λ ≥ 420 nm)	TCH Cr(vi)	$\text{O}_2^{\cdot-}/\text{h}^+$ e^-	96 98	149
Sm-g-C ₃ N ₄ /Ti ₃ C ₂	Stepwise synthesis	20 mg catalyst dispersed in 100 mL CIP (20 mg L ⁻¹)	300 W Xe lamp (λ ≥ 420 nm)	CIP	$\text{O}_2^{\cdot-}/\text{h}^+$	99	150
BiOBr/Ti ₃ C ₂	Solvothermal procedure	10 mg catalyst dispersed in 50 mL RhB (20 mg L ⁻¹)	300 W Xe lamp (λ ≥ 420 nm)	RhB	$\text{O}_2^{\cdot-}$	99.3/0.23043	151
IN-Ti ₃ C ₂ /TiO ₂	Stepwise synthesis	10 mg catalyst dispersed in 50 mL MB (20 mg L ⁻¹)	300 W Hg lamp (λ < 365 nm)	MB	$\cdot\text{OH}$	0.02642	152
WO ₃ /Ti ₃ C ₂ /In ₂ S ₃	Ultrasonic assisted self-assembly process	5 mg catalyst dispersed in 10 mL BPA (10 mg L ⁻¹)	30 W Xe lamp	BPA	$\text{O}_2^{\cdot-}$	97.6	153
NiCo ₂ S ₄ /Ti ₃ C ₂	Hydrothermal procedure	10 mg catalyst dispersed in 20 mL Cr(vi) (20 mg L ⁻¹)	30 W catalyst dispersed in 20 mL	Cr(vi)	e^-	99.8	154
Ti ₃ C ₂ /SnNb ₂ O ₆	Ultrasonic-assisted hydrothermal method	5 mg catalyst dispersed in 50 mL RhB (50 mg L ⁻¹)	250 W Xe lamp (400–800 nm)	RhB	$\text{O}_2^{\cdot-}/\cdot\text{OH}$	100	155
Ti ₃ C ₂ /Ag ₂ S	Ultrasonic assisted self-assembly process	15 mg catalyst dispersed in 60 mL TCH (10 mg L ⁻¹) and RhB (10 mg L ⁻¹)	300 W Xe lamp (λ ≥ 420 nm)	TCH RhB	$\cdot\text{OH}$ h^+	70/0.0145 98/0.0579	156
ZnS/Ti ₃ C ₂	Ultrasonic assisted self-assembly process	50 mg catalyst dispersed in 100 mL MB (20 mg L ⁻¹)	300 W Xe lamp (λ ≥ 420 nm)	MB MB RhB MO MR RhB	$\text{O}_2^{\cdot-} > \text{e}^- > \text{h}^+$ $\cdot\text{OH}$	98/0.08222 99.2/0.99198 99.54/0.99538 96.98/0.96985 87.45/0.87451 0.02464	157

^a Results included in studies published starting from 2020 onwards only; RhB: rhodamine B; CIP: ciprofloxacin; BPA: bisphenol A; TC: tetracycline; PMS: peroxymonosulfate; DCF: diclofenac; MO: methyl orange; TCH: tetracycline hydrochloride; IN: isopropyl amine modified; MB: methylene blue; PFOA: perfluorooctanoic acid; MR: methyl red; np: information not provided by authors.

a result charge separation, and (iii) redox processes initiated by these radicals.

While the photogenerated holes react with surface bound water molecules or hydroxyl groups (OH^-) to produce the hydroxyl radical ($\cdot\text{OH}$), photogenerated electrons interact with oxygen and generate anionic superoxide radicals ($\text{O}_2^{\cdot-}$). These are the most common radicals formed on the surface of photocatalysts, with the hydroperoxyl radical ($\text{HOO}\cdot$) being produced through a $\text{O}_2^{\cdot-}$ protonation process.

The $\cdot\text{OH}$ radicals are extremely powerful oxidizing agents that initiate a non-selective oxidative attack over the adsorbed organic molecules or those that are close to the photocatalyst surface, causing them to mineralize to an extent depending upon their structure and stability level.¹²² On the other hand, the $\text{O}_2^{\cdot-}$ radicals not only initiate further oxidation processes but also prevent charge recombination.

It should be noted that during the photocatalytic degradation processes, the inherent presence of oxidative radicals in the reaction medium, the UV light irradiation and the photo-thermal effect induced by the near-infrared irradiation may oxidize the $\text{Ti}_3\text{C}_2\text{T}_x$ surfaces.^{94,123} On the other hand, the target dye molecules (especially the cationic ones) can be adsorbed on the MXene surfaces and might change/affect their surface and electronic states.^{124,125} In this regard, it is clear that the reactions and interactions between $\text{Ti}_3\text{C}_2\text{T}_x$ and the aqueous environment are complicated and more detailed investigations (preferably operando and *in situ*) are needed to reveal the true working mechanism of the photocatalytic degradation processes on the surface of MXene-based composites.

As shown in Table 4, the photocatalytic degradation reactions of various pollutants (*e.g.*, methylene blue, methyl orange, bisphenol A, rhodamine B, diclofenac, tetracycline or tetracycline hydrochloride, among others) or the removal of toxic metals (*i.e.*, reduction of $\text{Cr}(\text{vi})$ anions) from water are the most studied applications of $\text{Ti}_3\text{C}_2\text{T}_x$ -based photocatalysts. Once again, the introduction of $\text{Ti}_3\text{C}_2\text{T}_x$ within a photocatalytic composite improves the photoactivity mainly due to the promotion of the separation of charge carriers and the presence of abundant surface groups and active sites where the targeted molecules are easily adsorbed.

5.5. Applications in N_2 photofixation and other photocatalytic/photo-assisted processes

In addition to photocatalytic applications presented above, there are many other cases in which $\text{Ti}_3\text{C}_2\text{T}_x$ is used as a co-catalyst in photocatalytic systems for different reduction and oxidation processes, such as the N_2 reduction reaction,^{126–129} photocatalytic bireforming of methane,¹³⁰ NO oxidation¹³¹ or photo-assisted organic transformations,¹³² among others.

The N_2 reduction reaction (NRR) under light irradiation, a process known as N_2 photofixation, has been investigated over different $\text{Ti}_3\text{C}_2\text{T}_x$ -based materials. Thus, Huo *et al.*¹²⁷ recently developed a highly active photocatalyst toward near-infrared light-driven N_2 photofixation by fabricating a plasmonic hybrid $\text{Ti}_3\text{C}_2\text{T}_x/\text{TiO}_2$ structure. The photocatalytic system attained a NH_3 production rate of $422 \mu\text{mol g}^{-1} \text{h}^{-1}$ under full-spectrum

irradiation. The authors also demonstrate that oxygen vacancies found on the surface served as the active centers for the adsorption and the activation of N_2 gas molecules.

By using $\text{Ti}_3\text{C}_2\text{T}_x$ as a precursor, Qian *et al.*¹²⁸ synthesized, through a one-step calcination approach, oxygen vacancy-rich C/TiO_2 materials that showed remarkable activity for the NRR. Thus, by using H_2O and CH_3OH as proton sources, they were able to produce NH_3 at rates of $41 \mu\text{mol g}^{-1} \text{h}^{-1}$ and $84 \mu\text{mol g}^{-1} \text{h}^{-1}$, respectively. Once again, the importance of oxygen vacancies in the efficiency of N_2 adsorption and activation was revealed by electron spin-resonance spectroscopy, ESR, and temperature programmed desorption of nitrogen, N_2 -TPD, experiments which showed that the chemisorption of N_2 is much more efficient on the surface of C/TiO_2 possessing higher concentrations of oxygen vacancies than in the case of commercial TiO_2 .

In line with the above, Gao *et al.*¹²⁹ reported the performance of the NRR over the $\text{Ti}_3\text{C}_2\text{T}_x/\text{TiO}_2/\text{Co}$ composite synthesized by introducing Co into the MXene@ TiO_2 catalysts in which the TiO_2 nanoparticles were derived from the *in situ* growth on the surface of MXene nanosheets. The optimal photocatalyst (containing 0.5 wt% Co) shows a NH_4^+ production rate of $110 \mu\text{mol g}^{-1} \text{h}^{-1}$ without the addition of any hole scavengers and under UV-vis light irradiation conditions.

The photocatalytic bireforming of CH_4 under visible light irradiation over Ti_3C_2 nanosheets coupled with a 2D $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction was investigated by Khan *et al.*¹³⁰ The authors demonstrate that the as-prepared photocatalytic composite shows CO and H_2 production rates of 48.4 and 83.2 $\mu\text{mol g}^{-1}$, reaching apparent quantum yields as high as 0.41 and 0.7%, respectively.

Another example of the use of gas phase photocatalysis over $\text{Ti}_3\text{C}_2\text{T}_x$ -based composites is the photocatalytic oxidation of nitric oxide (NO). In line with this research, Li *et al.*¹³¹ reported the use of a $\text{Ti}_3\text{C}_2/g\text{-C}_3\text{N}_4$ composite with an enhanced photocatalytic NO removal efficiency. Thus, the authors performed the photocatalytic oxidation of NO, and through monitoring by *in situ* diffuse reflectance infrared spectroscopy, they demonstrated that the final products were nitrite and nitrate instead of the undesired and toxic NO_2 .

Visible-light induced one-pot hydrogenation and amidation of nitroaromatics with carboxylic acids was recently investigated by Jiang *et al.*¹³² The authors prepared $\text{Pt}/\text{N-TiO}_2/\text{Ti}_3\text{C}_2$ heterojunctions by *in situ* growth of TiO_2 on Ti_3C_2 nanosheets and then N doped the TiO_2 with melamine, followed by the deposition of Pt nanoparticles. Thus, by using the 3 wt% $\text{Pt}/\text{N-TiO}_2/\text{Ti}_3\text{C}_2$ photocatalyst and in the presence of a K_3PO_4 additive, the hydrogenation and amidation reaction of nitrobenzene with acetic acid reached 100% conversion with 100% chemoselectivity to acetanilide.

6. Concluding remarks

In this review we have shown that the MAX phases and MXenes, with different chemical compositions, can be considered as potential catalysts, as well as supports, creating synergy with various active species. In some cases, their catalytic activity was

similar, or even better, compared with that of noble metal containing catalysts, highlighting, once again, their catalytic capabilities. At the current stage, these materials are proving to be extremely promising in various catalytic applications; however their surface chemistry and thermal stability are not fully understood.

Currently, MXenes cannot be applied in industrial processes as their large-scale production is not yet possible due to the HF involved in the synthesis that cannot be used in large quantities. Progress is expected in the synthesis method to avoid the use of HF, so that the remarkable properties observed for these materials in heterogeneous catalytic reactions can be improved further, to make their industrialization possible.

Depending on the application, these materials have been shown to be extremely resistant to coke, or if deactivation has been observed, it has been much slower than in the case of standard catalysts. One of the best ways to counteract this issue is by tuning the chemical composition and surface terminations.

Finally, we would like to draw attention to the two subclasses of these materials that have not yet been explored in heterogeneous catalytic reactions, other than electrochemical ones, namely the double $M'M''AX$ phase, obtained by alloying a MAX phase with another metal, and *i*-MXenes (in-plane ordered MXenes).¹⁵⁸ Usually, alloying of a MAX phase with another metal leads to chemically disordered solid solutions that can be an advantage in catalytic applications which are dependent on surface defects. Likewise, in the case of *i*-MXenes, the etching process results in 2D MXene structures with ordered vacancies, ordered divacancies or disordered vacancies with huge potential in catalytic applications.¹⁵⁸ The development of these materials is still in its infancy, but we predict a rapid evolution because the presence of vacancies and how they can influence the properties of the final catalytic material, is not only scientifically rewarding for any researchers, but also has major implications in the development of new materials for a variety of practical applications.

As compared with the oxide-based catalysts, MAX phases and MXenes have not been widely investigated as catalysts in traditional heterogeneous processes. However, further theoretical and experimental concerted studies will pave the way for new heterogeneous applications, such as selective oxidation of different hydrocarbons to value added compounds, and also in total oxidation reactions. Furthermore, appropriate modification of their surface or intercalation between the layers of different chemical compounds, will open new avenues for MAX phases and MXenes to be used as heterogeneous catalysts (*e.g.*, oxidative coupling of amines to imines).

Lastly a word of caution: MXenes are unstable in aqueous environments in which there is dissolved oxygen. In some cases, the oxidation occurs by hydrolysis,¹²³ and thus reducing the dissolved oxygen does not solve the problem. There are ways to mitigate oxidation^{159,160} but whether such approaches solve the long-term problem, especially in an open system, is an open question at this time. If this problem is not solved and/or shown not to be an issue, then all the work in that domain will be totally academic with no practical applications. Along the same

lines and somewhat ironically, it follows that oxidizing the MXenes to their more stable oxides and possibly C^{104} as some have done, may be an advisable and fruitful way forward.

Summarizing, it is clear that there is room for improvement in the design and synthesis of MAX phases and MXene based catalysts and in this regard several strategies can be adopted, such as tuning the chemical composition, ratios between elements, or surface terminations. As shown by the studies presented in this review, the deposition of different chemical species (transition metal oxides and metals) on MAX phase or MXene materials can lead to new different compounds/structures that have never been reported as a “classical support”, which leads us to believe that these materials are not sufficiently explored, and represent a vast reservoir of both knowledge and potential applications.

Author contributions

I. M. C. contributed to Section 3, A. G. M. contributed to Section 4, S. N. contributed to Section 5, while M. F., M. W. B. and F. N. contributed to the remaining sections with scientific writing, illustrations and table drafting. M. F., M. W. B. and F. N. supervised the research work and contributed to funding acquisition, outline drafting, reviewing, and editing the overall text, illustrations and tables of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by a grant of the Ministry of Research, Innovation and Digitization, CNCS/CCCDI – UEFISCDI, project number PN-III-P1-1.1-TE-2019-1969, within PNCDI III. MWB acknowledges the support of the Division of Materials Research of NSF (DMR 1740795).

References

- 1 M. W. Barsoum, *Prog. Solid State Chem.*, 2000, **28**, 201–281.
- 2 M. Naguib, M. Kurtoglu, V. Presser, J. Lu, J. Niu, M. Heon, L. Hultman, Y. Gogotsi and M. W. Barsoum, *Adv. Mater.*, 2011, **23**, 4248–4253.
- 3 M. W. Barsoum, *MAX Phases: Properties of Machinable Ternary Carbides and Nitrides*, Wiley-VCH Verlag, 2013.
- 4 M. Sokol, V. Natu, S. Kota and M. W. Barsoum, *Trends Chem.*, 2019, **1**, 210–223.
- 5 L. Verger, V. Natu, M. Carey and M. W. Barsoum, *Trends Chem.*, 2019, **1**, 656–669.
- 6 W. H. K. Ng, E. S. Gnanakumar, E. Batyrev, S. K. Sharma, P. K. Pujari, H. F. Greer, W. Zhou, R. Sakidja, G. Rothenberg, M. W. Barsoum and N. R. Shiju, *Angew. Chem., Int. Ed.*, 2018, **57**, 1485–1490.
- 7 P. Eklund, M. Beckers, U. Jansson, H. Högberg and L. Hultman, *Thin Solid Films*, 2010, **518**, 1851–1878.
- 8 Z. M. Sun, *Int. Mater. Rev.*, 2011, **56**, 143–166.

- 9 P. Eklund, J. Rosen and P. O. Å. Persson, *J. Phys. D: Appl. Phys.*, 2017, **50**, 113001.
- 10 L. Verger, C. Xu, V. Natu, H.-M. Cheng, W. Ren and M. W. Barsoum, *Curr. Opin. Solid State Mater. Sci.*, 2019, **23**, 149–163.
- 11 J. K. Im, E. J. Sohn, S. Kim, M. Jang, A. Son, K.-D. Zoh and Y. Yoon, *Chemosphere*, 2021, **270**, 129478.
- 12 L. Yu, B. Liu, Y. Wang, F. Yu and J. Ma, *J. Power Sources*, 2021, **490**, 229250.
- 13 Q. Zhong, Y. Li and G. Zhang, *Chem. Eng. J.*, 2021, **409**, 128099.
- 14 X. Li, Y. Bai, X. Shi, N. Su, G. Nie, R. Zhang, H. Nie and L. Ye, *Mater. Adv.*, 2021, **2**, 1570–1594.
- 15 Y. Zhang, X. Zhang, C. Cheng and Z. Yang, *Chin. Chem. Lett.*, 2020, **31**, 931–936.
- 16 C. Yang, H. Huang, H. He, L. Yang, Q. Jiang and W. Li, *Coord. Chem. Rev.*, 2021, **435**, 213806.
- 17 Z. Xia, Q. Huang and S. Guo, *FlatChem*, 2019, **17**, 100129.
- 18 M. A. Gibson and J. W. Hightower, *J. Catal.*, 1976, **41**, 420–430.
- 19 E. H. Lee, *Catal. Rev.*, 1974, **8**, 285–305.
- 20 G. Busca, in *Heterogeneous Catalytic Materials*, ed. G. Busca, Elsevier, Amsterdam, 2014, pp. 375–419.
- 21 C. Doornkamp and V. Ponec, *J. Mol. Catal. A: Chem.*, 2000, **162**, 19–32.
- 22 F. Cavani, N. Ballarini and A. Cericola, *Catal. Today*, 2007, **127**, 113–131.
- 23 J. Diao, M. Hu, Z. Lian, Z. Li, H. Zhang, F. Huang, B. Li, X. Wang, D. S. Su and H. Liu, *ACS Catal.*, 2018, **8**, 10051–10057.
- 24 J. Diao, Z. Feng, R. Huang, H. Liu, S. B. A. Hamid and D. S. Su, *ChemSusChem*, 2016, **9**, 662–666.
- 25 D. S. Su, S. Perathoner and G. Centi, *Chem. Rev.*, 2013, **113**, 5782–5816.
- 26 Z. Li, Y. Cui, Z. Wu, C. Milligan, L. Zhou, G. Mitchell, B. Xu, E. Shi, J. T. Miller, F. H. Ribeiro and Y. Wu, *Nat. Catal.*, 2018, **1**, 349–355.
- 27 Z. Li, L. Yu, C. Milligan, T. Ma, L. Zhou, Y. Cui, Z. Qi, N. Libretto, B. Xu, J. Luo, E. Shi, Z. Wu, H. Xin, W. N. Delgass, J. T. Miller and Y. Wu, *Nat. Commun.*, 2018, **9**, 5258.
- 28 B. Qiao, A. Wang, X. Yang, L. F. Allard, Z. Jiang, Y. Cui, J. Liu, J. Li and T. Zhang, *Nat. Chem.*, 2011, **3**, 634–641.
- 29 X. Sun, Y. Gao, C. Zhao, S. Deng, X. Zhong, G. Zhuang, Z. Wei and J. Wang, *Adv. Theory Simul.*, 2019, **2**, 1800158.
- 30 A. Kurlov, E. B. Deeva, P. M. Abdala, D. Lebedev, A. Tsoukalou, A. Comas-Vives, A. Fedorov and C. R. Müller, *Nat. Commun.*, 2020, **11**, 4920.
- 31 C. M. Damaskinos, M. A. Vasiliades and A. M. Efstathiou, *Appl. Catal., A*, 2019, **579**, 116–129.
- 32 L. Foppa, M.-C. Silaghi, K. Larmier and A. Comas-Vives, *J. Catal.*, 2016, **343**, 196–207.
- 33 R. Thakur, A. VahidMohammadi, J. Smith, M. Hoffman, J. Moncada, M. Beidaghi and C. A. Carrero, *ACS Catal.*, 2020, **10**, 5124–5134.
- 34 Z. Liu, D. C. Grinter, P. G. Lustemberg, T. D. Nguyen-Phan, Y. Zhou, S. Luo, I. Waluyo, E. J. Crumlin, D. J. Stacchiola and J. Zhou, *Angew. Chem., Int. Ed.*, 2016, **55**, 7455.
- 35 R. Thakur, M. Hoffman, A. VahidMohammadi, J. Smith, M. Chi, B. Tatarchuk, M. Beidaghi and C. A. Carrero, *ChemCatChem*, 2020, **12**, 3639–3643.
- 36 R. Thakur, A. VahidMohammadi, J. Moncada, W. R. Adams, M. Chi, B. Tatarchuk, M. Beidaghi and C. A. Carrero, *Nanoscale*, 2019, **11**, 10716–10726.
- 37 M. Ronda-Lloret, V. S. Marakatti, W. G. Sloof, J. J. Delgado, A. Sepúlveda-Escribano, E. V. Ramos-Fernandez, G. Rothenberg and N. R. Shiju, *ChemSusChem*, 2020, **13**, 6401–6408.
- 38 X. Zhang, J. Lei, D. Wu, X. Zhao, Y. Jing and Z. Zhou, *J. Mater. Chem. A*, 2016, **4**, 4871–4876.
- 39 C. Cheng, X. Zhang, M. Wang, S. Wang and Z. Yang, *Phys. Chem. Chem. Phys.*, 2018, **20**, 3504–3513.
- 40 Y. Li, Z. Zhou, G. Yu, W. Chen and Z. Chen, *J. Phys. Chem. C*, 2010, **114**, 6250–6254.
- 41 E. H. Song, Z. Wen and Q. Jiang, *J. Phys. Chem. C*, 2011, **115**, 3678–3683.
- 42 T.-T. Jia, C.-H. Lu, K.-N. Ding, Y.-F. Zhang and W.-K. Chen, *Comput. Theor. Chem.*, 2013, **1020**, 91–99.
- 43 J. L. Shi, J. H. Wu, X. J. Zhao, X. L. Xue, Y. F. Gao, Z. X. Guo and S. F. Li, *Nanoscale*, 2016, **8**, 19256–19262.
- 44 C. Cheng, X. Zhang, Z. Yang and K. Hermansson, *Adv. Theory Simul.*, 2019, **2**, 1900006.
- 45 H. Oschinski, Á. Morales-García and F. Illas, *J. Phys. Chem. C*, 2021, **125**, 2477–2484.
- 46 M. Manadé, F. Viñes and F. Illas, *Carbon*, 2015, **95**, 525.
- 47 S. Kim, A. Ruiz Puigdollers, P. Gamallo, F. Viñes and J. Y. Lee, *Carbon*, 2017, **120**, 63.
- 48 S. H. Talib, S. Baskaran, X. Yu, Q. Yu, B. Bashir, S. Muhammad, S. Hussain, X. Chen and J. Li, *Sci. China Mater.*, 2021, **64**, 651–663.
- 49 E. B. Deeva, A. Kurlov, P. M. Abdala, D. Lebedev, S. M. Kim, C. P. Gordon, A. Tsoukalou, A. Fedorov and C. R. Müller, *Chem. Mater.*, 2019, **31**, 4505.
- 50 D. Damma, T. Boningari and P. G. Smirniotis, *Mol. Catal.*, 2018, **451**, 20.
- 51 G. Wang, J. A. Schaidle, M. B. Katz, Y. Li, X. Pan and L. T. Thompson, *J. Catal.*, 2013, **304**, 92.
- 52 G. Fan, X. Li, C. Xu, W. Jiang, Y. Zhang, D. Gao, J. Bi and Y. Wang, *Nanomaterials*, 2018, **8**, 141.
- 53 Z. Li and Y. Wu, *Small*, 2019, **15**, 1–10.
- 54 M. Naguib, M. Kurtoglu, V. Presser, J. Lu, J. Niu, M. Heon, L. Hultman, Y. Gogotsi and M. W. Barsoum, *Adv. Mater.*, 2011, **23**, 4248–4253.
- 55 M. Naguib, V. N. Mochalin, M. W. Barsoum and Y. Gogotsi, *Adv. Mater.*, 2014, **26**, 992–1005.
- 56 B. Zielińska, A. Wróblewska, K. Maślana, P. Miądlicki, K. Kielbasa, A. Rozmysłowska-Wojciechowska, M. Petrus, J. Woźniak, A. M. Jastrzębska, B. Michalkiewicz and E. Mijowska, *Appl. Catal., A*, 2020, **604**, 117765.
- 57 J. B. Sharmeen, F. M. Mahomoodally, G. Zengin and F. Maggi, *Molecules*, 2021, **26**, 666.
- 58 N. Girola, C. R. Figueiredo, C. F. Farias, R. A. Azevedo, A. K. Ferreira, S. F. Teixeira, T. M. Capello, E. G. A. Martins, A. L. Matsuo, L. R. Travassos and

- J. H. G. Lago, *Biochem. Biophys. Res. Commun.*, 2015, **467**, 928–934.
- 59 D. Formenti, F. Ferretti, F. K. Scharnagl and M. Beller, *Chem. Rev.*, 2019, **119**, 2611–2680.
- 60 D. Wang and D. Astruc, *Chem. Rev.*, 2015, **115**, 6621–6686.
- 61 H.-U. Blaser, C. Malan, B. Pugin, F. Spindler, H. Steinei and M. Studer, *Adv. Synth. Catal.*, 2003, **345**, 103–151.
- 62 M. Crespo-Quesada, F. Cardenas-Lizana, A.-L. Dessimoz and L. Kiwi-Minsker, *ACS Catal.*, 2012, **2**, 1773–1786.
- 63 G. Vile, D. Albani, N. Almora-Barrios, N. López and J. Pórez-Ramirez, *ChemCatChem*, 2016, **8**, 21–33.
- 64 H. U. Blaser, H. Steiner and M. Studer, *ChemCatChem*, 2009, **1**, 210–221.
- 65 K. Li, T. Jiao, R. Xing, G. Zou, Q. Zhao, J. Zhou, L. Zhang and Q. Peng, *Green Energy Environ.*, 2018, **3**, 147–155.
- 66 P. Hervés, M. Pérez-Lorenzo, L. M. Liz-Marzán, J. Dzubielia, Y. Lu and M. Ballauff, *Chem. Soc. Rev.*, 2012, **41**, 5577–5587.
- 67 K. S. Egorova and V. P. Ananikov, *Angew. Chem., Int. Ed.*, 2016, **55**, 12150–12162.
- 68 L. Zhang, Z. J. Shao, X. M. Cao and P. Hu, *J. Phys. Chem. C*, 2018, **122**, 20337–20350.
- 69 X. Xie, Z. Wu and N. Zhang, *Chin. Chem. Lett.*, 2020, **31**, 1014–1017.
- 70 M. Ghidui, J. Halim, S. Kota, D. Bish, Y. Gogotsi and M. W. Barsoum, *Chem. Mater.*, 2016, **28**, 3507–3514.
- 71 M. M. Trandafir, F. Neațu, I. M. Chirica, Ș. Neațu, A. C. Kuncser, E. I. Cucolea, V. Natu, M. W. Barsoum and M. Florea, *ACS Catal.*, 2020, **10**, 5899–5908.
- 72 Q. Chen, W. Jiang and G. Fan, *Dalton Trans.*, 2020, **49**, 14914–14920.
- 73 J. P. Lange, E. Van Der Heide, J. Van Buijtenen and R. Price, *ChemSusChem*, 2012, **5**, 150–166.
- 74 M. Naguib, W. Tang, K. L. Browning, G. M. Veith, V. Maliekkal, M. Neurock and A. Villa, *ChemCatChem*, 2020, **12**, 5733–5742.
- 75 A. Fayyaz, K. Saravanakumar, K. Talukdar, Y. Kim, Y. Yoon and C. M. Park, *Chem. Eng. J.*, 2021, **407**, 127842.
- 76 M. Ding, W. Chen, H. Xu, Z. Shen, T. Lin, K. Hu, Q. Kong, G. Yang and Z. Xie, *Chem. Eng. J.*, 2019, **378**, 122177.
- 77 M. Ding, W. Chen, H. Xu, Z. Shen, T. Lin and K. Hu, *J. Hazard. Mater.*, 2020, **382**, 121064.
- 78 Y. Ma, X. Lv, D. Xiong, X. Zhao and Z. Zhang, *Appl. Catal., B*, 2021, **284**, 119720.
- 79 S. Luo, R. Wang, J. Yin, T. Jiao, K. Chen, G. Zou, L. Zhang, J. Zhou, L. Zhang and Q. Peng, *ACS Omega*, 2019, **4**, 3946–3953.
- 80 Y. Cui, M. Liu, H. Huang, D. Zhang, J. Chen and L. Mao, *Ceram. Int.*, 2020, **46**, 11593–11601.
- 81 Y. Liu, R. Luo, Y. Li, J. Qi, C. Wang, J. Li, X. Sun and L. Wang, *Chem. Eng. J.*, 2018, **347**, 731–740.
- 82 K. Han, X. Zhang, P. Deng, Q. Jiao and E. Chu, *Vacuum*, 2020, **180**, 109572.
- 83 L. Zhao, Y. Ji, D. Kong, J. Lu, Q. Zhou and X. Yin, *Chem. Eng. J.*, 2016, **303**, 458–466.
- 84 Y. Gao, L. Wang, Z. Li, A. Zhou, Q. Hu and X. Cao, *Solid State Sci.*, 2014, **35**, 62–65.
- 85 K. Li, Y. Lei, J. Liao and Y. Zhang, *Inorg. Chem. Front.*, 2021, **8**, 1747–1761.
- 86 M. A. Fox and M. T. Dulay, *Chem. Rev.*, 1993, **93**, 341–357.
- 87 F. Neațu, L. E. Abramiuc, M. M. Trandafir, R. F. Negrea, M. Florea, C. M. Teodorescu and S. Neațu, *ChemCatChem*, 2020, **12**, 4642–4651.
- 88 A. O. Ibhaddon and P. Fitzpatrick, *Catalysts*, 2013, **3**, 189–218.
- 89 J. Ran, G. Gao, F.-T. Li, T.-Y. Ma, A. Du and S.-Z. Qiao, *Nat. Commun.*, 2017, **8**, 13907.
- 90 H.-J. Lin, Q.-L. Mo, S. Xu, Z.-Q. Wei, X.-Y. Fu, X. Lin and F.-X. Xiao, *J. Catal.*, 2020, **391**, 485–496.
- 91 T. Schultz, N. C. Frey, K. Hantanasirisakul, S. Park, S. J. May, V. B. Shenoy, Y. Gogotsi and N. Koch, *Chem. Mater.*, 2019, **31**, 6590–6597.
- 92 X. Sang, Y. Xie, M.-W. Lin, M. Alhabeab, K. L. Van Aken, Y. Gogotsi, P. R. C. Kent, K. Xiao and R. R. Unocic, *ACS Nano*, 2016, **10**, 9193–9200.
- 93 J. Krupka and W. Strupinski, *Appl. Phys. Lett.*, 2010, **96**, 82101.
- 94 X. Xie and N. Zhang, *Adv. Funct. Mater.*, 2020, **30**, 2002528.
- 95 C. Yu, L. Peng, Y. Zhu, G. Xie, Z. Wu, X. Xie and N. Zhang, *J. Mater. Chem. A*, 2021, DOI: 10.1039/D1ta02736k.
- 96 M.-Q. Yang, N. Zhang, M. Pagliaro and Y.-J. Xu, *Chem. Soc. Rev.*, 2014, **43**, 8240–8254.
- 97 C. Gómez-Navarro, R. T. Weitz, A. M. Bittner, M. Scolari, A. Mews, M. Burghard and K. Kern, *Nano Lett.*, 2007, **7**, 3499–3503.
- 98 Ș. Neațu, M. Puche, V. Fornés and H. Garcia, *Chem. Commun.*, 2014, **50**, 14643–14646.
- 99 Y. Jiao, Y. Zheng, M. Jaroniec and S. Z. Qiao, *Chem. Soc. Rev.*, 2015, **44**, 2060–2086.
- 100 B. Hinnemann, P. G. Moses, J. Bonde, K. P. Jørgensen, J. H. Nielsen, S. Horch, I. Chorkendorff and J. K. Nørskov, *J. Am. Chem. Soc.*, 2005, **127**, 5308–5309.
- 101 T. Song, L. Hou, B. Long, A. Ali and G. J. Deng, *J. Colloid Interface Sci.*, 2021, **584**, 474–483.
- 102 N. Zhao, Y. Hu, J. Du, G. Liu, B. Dong, Y. Yang, J. Peng, J. Li and M. Zhai, *Appl. Surf. Sci.*, 2020, **530**, 147247.
- 103 J. Liu, X. Kong, Y. Li, S. Zhu, Y. Liang, Z. Li, S. Wu, C. Chang, Z. Cui and X. Yang, *Appl. Surf. Sci.*, 2020, **530**, 147283.
- 104 M. Naguib, O. Mashtalir, M. R. Lukatskaya, B. Dyatkin, C. Zhang, V. Presser, Y. Gogotsi and M. W. Barsoum, *Chem. Commun.*, 2014, **50**, 7420–7423.
- 105 G. Zuo, Y. Wang, W. L. Teo, A. Xie, Y. Guo, Y. Dai, W. Zhou, D. Jana, Q. Xian, W. Dong and Y. Zhao, *Angew. Chem., Int. Ed.*, 2020, **59**, 11287–11292.
- 106 Y. Li, X. Chen, Y. Sun, X. Meng, Y. Dall'Agnese, G. Chen, C. Dall'Agnese, H. Ren, S. Sasaki, H. Tamiaki and X. Wang, *Adv. Mater. Interfaces*, 2020, **7**, 1902080.
- 107 J. Yin, F. Zhan, T. Jiao, W. Wang, G. Zhang, J. Jiao, G. Jiang, Q. Zhang, J. Gu and Q. Peng, *Sci. China Mater.*, 2020, **63**, 2228–2238.
- 108 Y. Liu, Y.-H. Li, X. Li, Q. Zhang, H. Yu, X. Peng and F. Peng, *ACS Nano*, 2020, **14**, 14181–14189.
- 109 J. Kang, S. Byun, S. Kim, J. Lee, M. Jung, H. Hwang, T. W. Kim, S. H. Song and D. Lee, *ACS Appl. Energy Mater.*, 2020, **3**, 9226–9233.

- 110 L. Cheng, Q. Chen, J. Li and H. Liu, *Appl. Catal., B*, 2020, **267**, 118379.
- 111 X. Du, T. Zhao, Z. Xiu, Z. Xing, Z. Li, K. Pan, S. Yang and W. Zhou, *Appl. Mater. Today*, 2020, **20**, 100719.
- 112 J. Li, L. Zhao, S. Wang, J. Li, G. Wang and J. Wang, *Appl. Surf. Sci.*, 2020, **515**, 145922.
- 113 Z. Ai, K. Zhang, B. Chang, Y. Shao, L. Zhang, Y. Wu and X. Hao, *Chem. Eng. J.*, 2020, **383**, 123130.
- 114 G. Zeng, Y. Cao, Y. Wu, H. Yuan, B. Zhang, Y. Wang, H. Zeng and S. Huang, *Appl. Mater. Today*, 2021, **22**, 100926.
- 115 J. Li, J. Li, C. Wu, Z. Li, L. Cai, H. Tang, Z. Zhou, G. Wang, J. Wang, L. Zhao and S. Wang, *Carbon*, 2021, **179**, 387–399.
- 116 B. Sun, P. Qiu, Z. Liang, Y. Xue, X. Zhang, L. Yang, H. Cui and J. Tian, *Chem. Eng. J.*, 2021, **406**, 127177.
- 117 Ş. Neaţu, J. Maciá-Agulló and H. Garcia, *Int. J. Mol. Sci.*, 2014, **15**, 5246–5262.
- 118 M. Que, Y. Zhao, Y. Yang, L. Pan, W. Lei, W. Cai, H. Yuan, J. Chen and G. Zhu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 6180–6187.
- 119 J. Zhang, J. Shi, S. Tao, L. Wu and J. Lu, *Appl. Surf. Sci.*, 2021, **542**, 148685.
- 120 X. Li, Y. Bai, X. Shi, J. Huang, K. Zhang, R. Wang and L. Ye, *Appl. Surf. Sci.*, 2021, **546**, 149111.
- 121 Y. Yang, D. Zhang, J. Fan, Y. Liao and Q. Xiang, *Sol. RRL*, 2021, **5**, 2000351.
- 122 A. Ajmal, I. Majeed, R. N. Malik, H. Idriss and M. A. Nadeem, *RSC Adv.*, 2014, **4**, 37003–37026.
- 123 T. Habib, X. Zhao, S. A. Shah, Y. Chen, W. Sun, H. An, J. L. Lutkenhaus, M. Radovic and M. J. Green, *npj 2D Mater. Appl.*, 2019, **3**, 8.
- 124 O. Mashtalir, K. M. Cook, V. N. Mochalin, M. Crowe, M. W. Barsoum and Y. Gogotsi, *J. Mater. Chem. A*, 2014, **2**, 14334–14338.
- 125 Q. Peng, J. Guo, Q. Zhang, J. Xiang, B. Liu, A. Zhou, R. Liu and Y. Tian, *J. Am. Chem. Soc.*, 2014, **136**, 4113–4116.
- 126 C. Hao, Y. Liao, Y. Wu, Y. An, J. Lin, Z. Gu, M. Jiang, S. Hu and X. Wang, *J. Phys. Chem. Solids*, 2020, **136**, 109141.
- 127 T. Hou, Q. Li, Y. Zhang, W. Zhu, K. Yu, S. Wang, Q. Xu, S. Liang and L. Wang, *Appl. Catal., B*, 2020, **273**, 119072.
- 128 J. Qian, S. Zhao, W. Dang, Y. Liao, W. Zhang, H. Wang, L. Lv, L. Luo, H.-Y. Jiang and J. Tang, *Adv. Sustainable Syst.*, 2021, **5**, 2000282.
- 129 W. Gao, X. Li, S. Luo, Z. Luo, X. Zhang, R. Huang and M. Luo, *J. Colloid Interface Sci.*, 2021, **585**, 20–29.
- 130 A. A. Khan, M. Tahir and A. Bafaqeer, *Energy Fuels*, 2020, **34**, 9810–9828.
- 131 J. Li, Q. Zhang, Y. Zou, Y. Cao, W. Cui, F. Dong and Y. Zhou, *J. Colloid Interface Sci.*, 2020, **575**, 443–451.
- 132 H. Jiang, Z. Hu, C. Gan, B. Sun, S. Kong and F. Bian, *Mol. Catal.*, 2021, **504**, 111490.
- 133 X. Liu and C. Chen, *Mater. Lett.*, 2020, **261**, 127127.
- 134 K. Wu, S. Song, H. Wu, J. Guo and L. Zhang, *Appl. Catal., A*, 2020, **608**, 117869.
- 135 Z. Miao, G. Wang, X. Zhang and X. Dong, *Appl. Surf. Sci.*, 2020, **528**, 146929.
- 136 X. Wang, Y. Yang, G. Lu, G. Shi, Y. Wang, R. Wang, X. Xie and J. Sun, *Appl. Surf. Sci.*, 2020, **531**, 147101.
- 137 H. Zhang, M. Li, C. Zhu, Q. Tang, P. Kang and J. Cao, *Ceram. Int.*, 2020, **46**, 81–88.
- 138 L. Chen, X. Ye, S. Chen, L. Ma, Z. Wang, Q. Wang, N. Hua, X. Xiao, S. Cai and X. Liu, *Ceram. Int.*, 2020, **46**, 25895–25904.
- 139 Z. Wu, Y. Liang, X. Yuan, D. Zou, J. Fang, L. Jiang, J. Zhang, H. Yang and Z. Xiao, *Chem. Eng. J.*, 2020, **394**, 124921.
- 140 T. Xu, J. Wang, Y. Cong, S. Jiang, Q. Zhang, H. Zhu, Y. Li and X. Li, *Chin. Chem. Lett.*, 2020, **31**, 1022–1025.
- 141 H. Liu, C. Yang, X. Jin, J. Zhong and J. Li, *Colloids Surf., A*, 2020, **603**, 125239.
- 142 J. Chen, H. Zheng, Y. Zhao, M. Que, X. Lei, K. Zhang and Y. Luo, *J. Phys. Chem. Solids*, 2020, **145**, 109565.
- 143 L. Zhang, J. Yang, T. Xie, S. Feng and L. Xu, *Mater. Des.*, 2020, **192**, 108772.
- 144 Q. Luo, J. Yang, Y. Wu and Q. Cai, *Micro Nano Lett.*, 2020, **15**, 764–768.
- 145 H. Song, Y. Wang, Z. Ling, D. Zu, Z. Li, Y. Shen and C. Li, *Sci. Total Environ.*, 2020, **746**, 141009.
- 146 B. Shao, Z. Liu, G. Zeng, Y. Liu, Q. Liang, Q. He, T. Wu, Y. Pan, J. Huang, Z. Peng, S. Luo, C. Liang, X. Liu, S. Tong and J. Liang, *Appl. Catal., B*, 2021, **286**, 119867.
- 147 B. Sun, F. Tao, Z. Huang, W. Yan, Y. Zhang, X. Dong, Y. Wu and G. Zhou, *Appl. Surf. Sci.*, 2021, **535**, 147354.
- 148 N. My Tran, Q. Thanh Hoai Ta and J.-S. Noh, *Appl. Surf. Sci.*, 2021, **538**, 148023.
- 149 Z. Zhuge, X. Liu, T. Chen, Y. Gong, C. Li, L. Niu, S. Xu, X. Xu, Z. A. Allothman, C. Q. Sun, J. G. Shapter and Y. Yamauchi, *Chem. Eng. J.*, 2020, 127838.
- 150 M. Yu, H. Liang, R. Zhan, L. Xu and J. Niu, *Chin. Chem. Lett.*, 2021, **32**, 2155–2158.
- 151 X. Meng, J. Song, J. Ren and J. Zhu, *CrystEngComm*, 2021, **23**, 1507–1516.
- 152 T. Ke, S. Shen, K. Rajavel, K. Yang and D. Lin, *J. Hazard. Mater.*, 2021, **402**, 124066.
- 153 Z. Yuan, H. Huang, N. Li, D. Chen, Q. Xu, H. Li, J. He and J. Lu, *J. Hazard. Mater.*, 2021, **409**, 125027.
- 154 S. Vigneshwaran, C. M. Park and S. Meenakshi, *Sep. Purif. Technol.*, 2021, **258**, 118003.
- 155 H. Wang, L. Chen, Y. Sun, J. Yu, Y. Zhao, X. Zhan and H. Shi, *Sep. Purif. Technol.*, 2021, **265**, 118516.
- 156 X. Feng, Z. Yu, Y. Sun, M. Shan, R. Long and X. Li, *Sep. Purif. Technol.*, 2021, **266**, 118606.
- 157 X. Liu, Q. Liu and C. Chen, *Vacuum*, 2021, **183**, 109834.
- 158 B. Ahmed, A. El Ghazaly and J. Rosen, *Adv. Funct. Mater.*, 2020, **30**, 2000894.
- 159 X. Zhao, D. E. Holta, Z. Tan, J.-H. Oh, I. J. Echols, M. Anas, H. Cao, J. L. Lutkenhaus, M. Radovic and M. J. Green, *ACS Appl. Nano Mater.*, 2020, **3**, 10578–10585.
- 160 V. Natu, J. L. Hart, M. Sokol, H. Chiang, M. L. Taheri and M. W. Barsoum, *Angew. Chem., Int. Ed.*, 2019, **58**, 12655–12660.