

# RSC Applied Interfaces

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: C. Tian, C. Maheu, X. Huang, F. Oropeza, M. Major, J. Brötz, M. Einert, W. Donner, K. H. L. Zhang and J. P. Hofmann, *RSC Appl. Interfaces*, 2024, DOI: 10.1039/D4LF00260A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## ARTICLE

# Evaluating the electronic structure and stability of epitaxially grown Sr-doped LaFeO<sub>3</sub> perovskite alkaline O<sub>2</sub> evolution model electrocatalysts

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Chuanmu Tian<sup>a</sup>, Clément Maheu<sup>a,b</sup>, Xiaochun Huang<sup>c</sup>, Freddy E. Oropeza<sup>d</sup>, Márton Major<sup>e</sup>, Joachim Brötz<sup>e</sup>, Marcus Einert<sup>a</sup>, Wolfgang Donner<sup>e</sup>, Kelvin Hongliang Zhang<sup>c</sup>, Jan P. Hofmann<sup>a\*</sup>

In this work, we have investigated the relationships between surface stability, electronic structure and O<sub>2</sub> evolution reaction (OER) activity for epitaxial thin film La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) model electrocatalysts before and after different electrochemical treatments. Cyclic voltammetry (CV) between +1.22 V and +1.92 V vs. RHE results in the continuous enhancement of OER performance of LaFeO<sub>3</sub>, while for La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> and La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub> a gradual decrease of OER performance with increasing number of CV cycles was observed. A combination of atomic force microscopy, X-ray diffraction and X-ray reflectivity reveals that the surfaces of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) undergo surface morphology changes during OER treatment. Synchrotron ex-situ X-ray photoemission spectroscopy data show a gradual down-shift of the Fermi level (*E<sub>F</sub>*) of LaFeO<sub>3</sub> with increasing number of CV cycles, while near edge X-ray absorption fine structure spectroscopy (NEXAFS) at the Fe L-edge and O K-edge shows the presence of surface Fe<sup>4+</sup> species as well as new hole states near the conduction band minimum upon electrochemical treatment, leading to a further enhancement of the electrochemical activity of LaFeO<sub>3</sub>. The newly formed hole state in LaFeO<sub>3</sub> that appeared after 3 CV cycles remained constant upon progressing OER treatment. On the contrary, the decrease of OER performance of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> and La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub> with increasing CV cycles is attributed to an up-shift of *E<sub>F</sub>* along with a decrease of Fe<sup>4+</sup> and hole state content after OER treatment. Furthermore, we found that the stability of the OER performance of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> is closely related to the leaching of Sr during OER, and the stability deteriorates with increasing Sr doping concentration in the pristine samples.

## Introduction

Electrochemical water splitting is a promising pathway for large-scale production of green hydrogen and is expected to contribute to solving global energy and environmental issues.<sup>1,2</sup> However, the oxygen evolution reaction (OER) limits the efficiency of the overall water electrolysis due to the higher overpotential caused by the kinetically demanding four electron/proton transfer process.<sup>3,4</sup> Therefore, the development of highly active and stable OER electrocatalysts is critical to water electrolysis. Currently, IrO<sub>2</sub>- and RuO<sub>2</sub>-based catalysts for water electrolysis have been considered as the best OER catalysts in acidic media owing to their excellent OER activity, but their scarcity and high cost hinder their large-scale application.<sup>5-7</sup> Hence, cheap, earth-abundant and stable transition metal oxides are becoming more

attractive, especially Fe, Co and Ni, when alkaline water electrolysis is considered.<sup>8-10</sup> Among them, the perovskite oxides have attracted great attention due to their low cost and tunable electronic structure.<sup>11-13</sup> Perovskite oxides have the general formula ABO<sub>3</sub>, where A is an alkaline earth metal cation (La, Ba, Sr, etc.) and B is a transition metal cation (Fe, Co, Ni, etc.).<sup>14</sup> Currently, in order to provide a design basis for optimally performing semiconducting perovskite oxide OER electrocatalysts, significant efforts are devoted to explore the relationship between the electronic structure and electrocatalytic activity of perovskite oxides with activity descriptor concepts such as the e<sub>g</sub> orbital occupancy,<sup>15</sup> p-band centre of the oxygen atom,<sup>16</sup> metal-oxygen covalency.<sup>17</sup>

LaFeO<sub>3</sub>, a typical perovskite oxide, has been widely studied due to its good stability in alkaline electrolytes and adjustable electronic structure.<sup>18,19</sup> Over the past decades, a series of strategies has been explored to enhance the electrochemical activity of LaFeO<sub>3</sub>, including nanostructure engineering to increase the surface area,<sup>20</sup> morphology design to expose more active crystal facets,<sup>21</sup> and aliovalent doping to increase the electrical conductivity and to modulate electronic structure.<sup>22-25</sup> Among them, aliovalent doping is a powerful method to enhance the OER activity of LaFeO<sub>3</sub>. Recently, we found that doping by Sr can significantly improve the OER performance of LaFeO<sub>3</sub>.<sup>26</sup> We argue that filled electronic states near the Fermi level (*E<sub>F</sub>*) improve the orbital overlap with key OER reaction intermediates, favouring their formation. At the same time, the hole states close to the *E<sub>F</sub>* increase the electron affinity of the LaFeO<sub>3</sub>, thereby facilitating charge transfer at the

<sup>a</sup> Surface Science Laboratory, Department of Materials- and Geosciences, Technical University of Darmstadt, Peter-Grünberg-Straße 4, 64287 Darmstadt, Germany.

<sup>b</sup> Université de Nantes, CNRS, Institut des Matériaux Jean Rouxel, IMN, F-44000 Nantes, France.

<sup>c</sup> State Key Laboratory of Physical Chemistry of Solid Surfaces, College of Chemistry and Chemical Engineering, Xiamen University, Siming South Street 422, Xiamen 3611005, P. R. China.

<sup>d</sup> Photoactivated Processes Unit, IMDEA Energy Institute, Parque Tecnológico de Móstoles, Avda. Ramón de la Sagra 3, 28935 Móstoles, Madrid, Spain.

<sup>e</sup> Department of Materials- and Geosciences, Technical University of Darmstadt, Peter-Grünberg-Straße 2, 64287 Darmstadt, Germany.

Supplementary Information available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



solid-electrolyte interface. Importantly, it has been observed that perovskite electrocatalysts usually undergo surface morphology and compositional changes during OER.<sup>27-34</sup> It is then almost impossible to predict the OER performance of electrocatalysts from their pristine (bulk and surface) composition and structure since their active surface phase can strongly differ from the bulk composition and structure.<sup>35</sup> Thus, it is critical to investigate the electronic structure and surface properties of the catalytically active surface, ideally under in-situ conditions. For example, Wan et al. reported that SrIrO<sub>3</sub> undergoes surface reconstruction accompanied by the formation of amorphous layers during electrochemical treatment.<sup>36</sup> They attributed the improved OER performance of SrIrO<sub>3</sub> to the formation of more active amorphous Sr<sub>y</sub>IrO<sub>x</sub> layer. Another typical perovskite with surface reconstruction is Ba<sub>0.5</sub>Sr<sub>0.5</sub>Co<sub>0.8</sub>Fe<sub>0.2</sub>O<sub>3-δ</sub> (BSCF).<sup>37</sup> Fabbri et al. used in-situ X-ray absorption spectroscopy (XAS) to reveal that the (Co/Fe)O(OH) layer, which formed by the surface reconstruction of BSCF, can be considered as the OER active surface phase.

Although we have established the relationship between the electronic structure of pristine Sr-doped LaFeO<sub>3</sub> powder-based electrocatalysts and their OER activity<sup>26</sup>, the stability of the surface chemical composition, morphology, and electronic structure as the OER progresses still needs to be investigated and verified. Therefore, in order to establish a relationship between the surface properties, i.e., surface chemical composition, atomic and electronic structure including their stabilities, and the OER activity of the Sr-doped LaFeO<sub>3</sub>, we have employed epitaxial La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (001) single crystalline films as models to exclude the effect of nanostructure. We prepared a series of well-defined La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) single crystal films on Nb-doped SrTiO<sub>3</sub> (001) substrate via pulsed laser deposition (PLD). Our result show that the OER performance of LaFeO<sub>3</sub> increases with increasing CV cycles, while the OER activity of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> and La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub> is gradually decreasing. The surface properties of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) were investigated by atomic force microscopy (AFM), X-ray diffraction (XRD) and X-ray reflectivity (XRR) before and after OER treatments. The combination of synchrotron X-ray photoemission spectroscopy (SXPS) and near edge X-ray absorption fine structure spectroscopy (NEXAFS) revealed electronic structure changes of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) upon OER treatment in the amount of surface Fe<sup>4+</sup> active species, hole state and occupied density of states (DOS) near the Femi level ( $E_f$ ).

## Experimental section

### Materials synthesis

La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) targets were synthesized by solid-phase reaction. Stoichiometric amounts of La<sub>2</sub>O<sub>3</sub> (Alfa, > 99.999%), Fe<sub>2</sub>O<sub>3</sub> (Alfa, > 99.999%) and SrO (Alfa, > 99.999%) were mixed in a mortar. After grinding for 2 hours, the powder was pressed into pellets through a hydraulic press at 10 tons for 2 minutes, and finally these pellets were calcined in a muffle furnace (Kejing, KSL-1700) at 1000 °C for 24 h with 5 °C/min heating rate, followed by natural cooling to room temperature. La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8, 1.0) single crystal thin films were grown on one-side polished (001)-oriented 0.1% Nb-doped SrTiO<sub>3</sub> substrates (HeFei Kejing) by PLD using the respective target. Laser ablation was performed at a repetition rate of 5 Hz and an energy density of 1.0 J/cm<sup>2</sup> with a 248 nm KrF excimer laser. To achieve ~40 nm film thickness, the laser was impinged on the target for 15 min with the substrate

temperature 550 °C and oxygen partial pressure of 30 mTorr.

[View Article Online](#)

DOI: 10.1039/D4LF00260A

### Materials characterization

The crystal structure of the pure La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> targets was analysed by X-ray diffraction (XRD) using Cu K $\alpha$  radiation generated at 40 kV and 44 mA. Thin film growth was examined by high-resolution X-ray diffraction using a rotating Cu anode (45 kV, 190 mA) Rigaku SmartLab diffractometer in  $\theta$ -2 $\theta$  geometry, equipped with a Ge (220) double bounce monochromator (selecting the Cu K $\alpha_1$  wavelength) in parallel beam mode, while the thickness of the films was determined by X-ray reflectivity (XRR) scans on the same diffractometer. The surface morphology of the La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> samples before and after OER treatments were determined by atomic force microscopy (AFM) with a Bruker Icon Dimension AFM in amplitude modulation mode using PPP-Zeihl cantilevers (NanoAndMore GmbH, Wetzlar, Germany). This type of cantilever has a nominal spring constant of 27 N/m, a nominal resonance frequency of 130 kHz, and a typical tip radius of <7 nm. A free oscillation amplitude  $A_0 \approx 120$  nm of the cantilever tip was adjusted, and a setpoint ratio of  $A_{sp}/A_0 \approx 0.7$  was set to ensure operation in the repulsive tip-sample interaction regime. We scanned the surface with a tip velocity of 2  $\mu$ m/s.

The SXPS and NEXAFS measurements were performed at the soft X-ray spectroscopy undulator beamline U49-2\_PGM-1 at BESSY II synchrotron in Berlin. The beamline provides photons in the energy range of 85 – 1600 eV. The Solid-Liquid-Interface Analysis System (SOLIAS) endstation has been used and spectra were measured at normal emission using a Phoibos 150 (SPECS) energy analyser with a 1D delay line detector.<sup>38</sup> An Ar-ion sputter-cleaned Au foil served as a calibration sample by making use of the Au4f<sub>7/2</sub> transition located at 84.0 eV. Samples were electrically connected to the ground of the spectrometer. Excitation energies were adjusted for each core level to measure the photoelectrons at identical kinetic energy of 550 eV, which allows investigation of each element at a comparable depth of analysis, i.e., three times the inelastic mean free path at 550 eV kinetic energy (1.2-1.3 nm). The NEXAFS measurements at the Fe L-edge and O K-edge were carried out by recording the Auger electron yield of the respective elements.

Electrochemical measurements were carried out in three-electrode configuration using a Palmsens electrochemical workstation (Palmsens BV, The Netherlands) setup in the double glass cross electrochemistry chamber of the SOLIAS endstation.<sup>38</sup> The chamber was continuously purged by argon keeping the sample under an inert, dry, and carbon-free atmosphere and minimizing atmospheric contamination between the electrochemical treatments and the synchrotron-based measurements. A platinum wire was used as a counter electrode and Hg/HgO (1 M KOH) as a reference electrode. Cyclic voltammetry (CV) measurements were performed in 1 M KOH at a scan rate of 10 mV/s with the potential from +1.22 to +1.92 V (vs. RHE). Each sample was subjected to four OER treatments, namely total 0 CV (exposure to electrolyte only), total 3 CV (+3 increment), total 10 CV (+7 increment), and total 30 CV (+20 increment) cycles. After each treatment step, the sample was rinsed with MilliQ water and blown dry by Ar, then transferred to the vacuum system of the SOLIAS endstation for spectroscopic investigation.


## Results and Discussion

### Structural characterization

XRD and XRR were employed to characterize the quality of the La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> thin films grown on 0.1% Nb-doped SrTiO<sub>3</sub> (001) substrates by PLD. Figure 1 shows the XRD and XRR results of the La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> in pristine state (black curve) and after 30 CV cycles (i.e., after all four electrochemical treatment steps, red



curve). The well-defined oscillations are observed in both XRD and XRR plots for pristine LaFeO<sub>3</sub> (LFO) and La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> (LSF-0.33), indicating the high quality of the thin films. However, these oscillations did not appear in the XRD plot (Figure 1c) of La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub> (LSF-0.8), which is attributed to the presence of a large number of oxygen vacancies in the LSF-0.8 sample causing the film not to grow epitaxial, similar as reported for SrCoO<sub>3-x</sub> and SrFeO<sub>3-x</sub>.<sup>39,40</sup> The

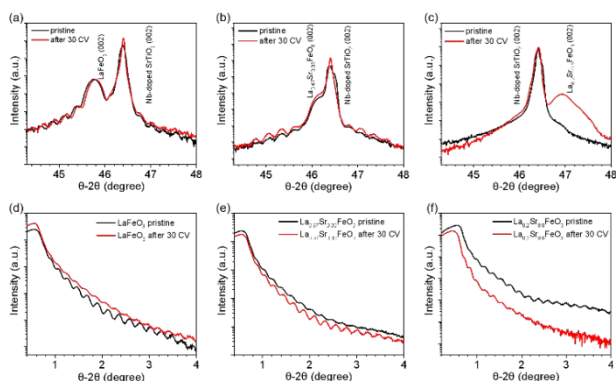


**Figure 1.** XRD and XRR of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> thin films in pristine state (black curves) and after 30 CV cycles (red curves). (a) XRD of LaFeO<sub>3</sub>, (b) XRD of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub>, (c) XRD of La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub>, (d) XRR of LaFeO<sub>3</sub>, (e) XRR of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> and (f) XRR of La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub>.

peak at  $2\theta = 46.4^\circ$  corresponds to the (002) orientation of the 0.1% Nb-doped SrTiO<sub>3</sub> single crystal substrate, while the peaks at  $2\theta = 45.8^\circ$ ,  $46.2^\circ$  and  $46.9^\circ$  correspond to (002) oriented LFO, LSF-0.33 and LSF-0.8, respectively. To determine the thickness of the La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> thin films, we obtained and fitted XRR data as shown in Figure S1, and the corresponding fitting parameters are reported in Table S1. The overall thickness of the pristine LFO, LSF-0.33 and LSF-0.8 single crystal thin films are  $37.5 \pm 0.5$  nm,  $38.6 \pm 0.2$  and  $39.2 \pm 0.2$ , respectively. After 30 CV cycles between +1.22 V to +1.92 V (vs. RHE) in 1 M KOH, there is a slight decrease in the thickness of the crystalline layer of all La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> ( $x = 0, 0.33$ ) thin films and an amorphous layer appears on all La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> ( $x = 0, 0.33$ ) film surfaces. The corresponding XRR plot of LFO before and after OER treatment is shown in Figure 1d. We also notice that the distance of the Kiessig fringes in the XRR plot of LFO remain consistent after 30 CV cycles, indicating negligible change of the overall film thickness. At the same time, the XRD (Figure 1b) and XRR (Figure 1e) data of LSF-0.33 show that the thickness of the crystalline layer as well as the overall thickness of the film remain unchanged. Figure 1c shows the XRD results of LSF-0.8 before and after 30 CV cycles; we notice that the peak intensity corresponding to LSF-0.8 increased after 30 CV, which is attributed to a surface reconstruction of LSF-0.8 thin film occurring under OER conditions. Based on the XRD and XRR results, we can state that the OER treatment resulted in an amorphous layer on the surface of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> ( $x = 0, 0.33$ ) samples. In addition, Table S1 compiles the roughness of all La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> ( $x = 0, 0.33, 0.8$ ) samples. After 30 CV cycles, the roughness of LFO and LSF-0.33 increased from 0.61 nm to 0.69 nm and 0.67 to 0.82, respectively, while the roughness decreased from 1.73 nm to 0.41 nm for LSF-0.8.

To further investigate the effect of OER treatment on the surface properties, we carried out AFM measurements on the pristine and OER-treated thin films. As shown in Figures S2a and S2c, the pristine LFO and LSF-0.33 have a flat surface with a root mean square roughness (RMS) of 0.50 nm and 0.30 nm, respectively, which further confirms the high quality of these films grown by

PLD. However, the RMS of pristine LSF-0.8 reaches 5.36 nm, which is much higher than LFO and LSF-0.33. Such a high RMS value of LSF-0.8 is attributable to the fact that it was not epitaxially grown on the 0.1% Nb-SrTiO<sub>3</sub> substrate, which is consistent with the above XRD results. After all four OER treatment steps, the RMS of LFO (Figure S2b) remained virtually unchanged. As shown in Figure S2c, the RMS of LSF-0.33 increased from the initial 0.30 nm to 1.12 nm after OER treatment. On the contrary, we notice that the RMS of LSF-0.8 (Figure S2f) is drastically reduced from 5.36 to 0.54 nm after OER treatment. Among them, the changes in the LSF-0.8 film due to OER treatment were the most pronounced, which is consistent with our XRD and XRR results.

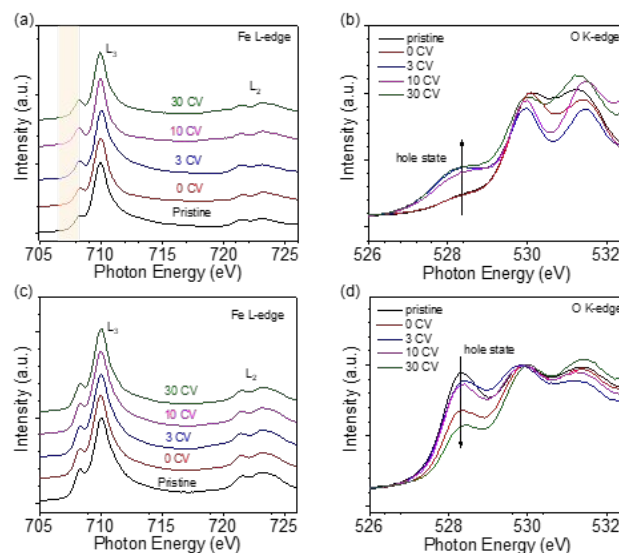

**Figure 2.** NEXAFS spectra of LaFeO<sub>3</sub> and La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> with different CV cycles. (a) Fe L-edge of LaFeO<sub>3</sub>, (b) O K-edge of LaFeO<sub>3</sub>, (c) Fe L-edge of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub> and (d) O K-edge of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub>. The yellow bars in Figure 2a indicate the changes in the characteristics of Fe<sup>3+</sup> and Fe<sup>4+</sup> at 708 eV under different CV cycles.

### Electronic structure by X-ray photoemission and absorption spectroscopies

The oxidation state of Fe was determined by NEXAFS of the Fe L-edge. Figure 2a shows the Fe L-edge of LFO after different OER treatment steps. The shape of the spectra of pristine and 0 CV samples are consistent with previously reported results for Fe<sup>3+</sup> oxidation state.<sup>26</sup> More importantly, the shape and intensity of the Fe L-edge remain consistent after 3 and even 30 CV cycles. To further investigate the oxidation state of Fe, we measured the O K-edge NEXAFS of LFO after different CV cycles, shown in Figure 2b. The results indicate that a new unoccupied (hole) state emerges at 528.4 eV, which is associated with Fe<sup>4+</sup> in agreement with our previous report.<sup>26</sup> More interestingly, this hole state exhibits the same behaviour after 3 and even 30 CV cycles. The Fe L-edge of pristine samples of LSF-0.33 (Figure 2c, black curve) and LSF-0.8 (Figure S3a, black curve) also exhibited Fe<sup>4+</sup> oxidation state characteristics, with LSF-0.8 being very similar to SrFeO<sub>3</sub>. However, the linear shape and intensity of the Fe L-edge of LSF-0.33 and LSF-0.8 both show slight changes at different CV cycles, suggesting that the Fe<sup>4+</sup> oxidation state still exists after OER treatment. At the same time, the intensity of the hole state features in the O K-edge spectra in LSF-0.33 (Figure 2d) and LSF-0.8 (Figure S3b) samples exhibit a gradually decreasing trend with increasing CV cycles,






indicating that the Fe<sup>4+</sup> content in LSF-0.33 and LSF-0.8 is gradually decreasing due to the fact that these hole states are closely related to the Fe<sup>4+</sup> oxidation state. Additionally, we still observe the presence of the hole state on the O K-edge even after 30 CV cycles, further confirming that Fe<sup>4+</sup> is still existent in LSF-0.33 and LSF-0.8 after different OER treatment steps. Taken together, the above results indicate that the OER treatment led to a morphology change of the La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> surface and the appearance of a hole state at LFO, while the hole state content of both LSF-0.33 and LSF-0.8 samples decreased after surface reconstruction.

In order to investigate the stability of the surface chemical composition and electronic structure of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) with increasing OER

spectrum of LFO in the Figure 3d show that the distance between the valence band maximum (VBM) and E<sub>F</sub> decreased with increasing CV number, indicating a downward movement of E<sub>F</sub> or alternatively an upward movement of the VBM.


Figure 4 summarizes the shift of the core levels and VB spectra, as well as the corresponding band energy schemes for LFO from the SXPS data. By combining the systematic shift of the binding energies of the Fe 2p, La 3d, and O 1s spectra together with the shift of the VB spectra, we can clarify the downward shift of E<sub>F</sub> with progressing CV cycling. More importantly, the above XRD and AFM data combined with the NEXAFS results indicate that the shift of E<sub>F</sub> can be attributed to the formation of Fe<sup>4+</sup> species on the LFO surface due to surface reconstruction during the OER process. Such a phenomenon has also been observed in different transition metal oxides, such as LaNiO<sub>3</sub> and SrIrO<sub>3</sub>.<sup>36,41</sup> The SXPS data of LFO-0.33 with different numbers of CV cycles are shown in Figure S4, respectively. In contrast to the LFO samples, the core levels of LSF-0.33 (Fe 3d, La 3d, and O 1s) shift to higher binding energies, and the distance between VBM and E<sub>F</sub> increased with increasing CV cycling, indicating a gradual upward movement of E<sub>F</sub> in LSF-0.33.

### Electrochemical characterization

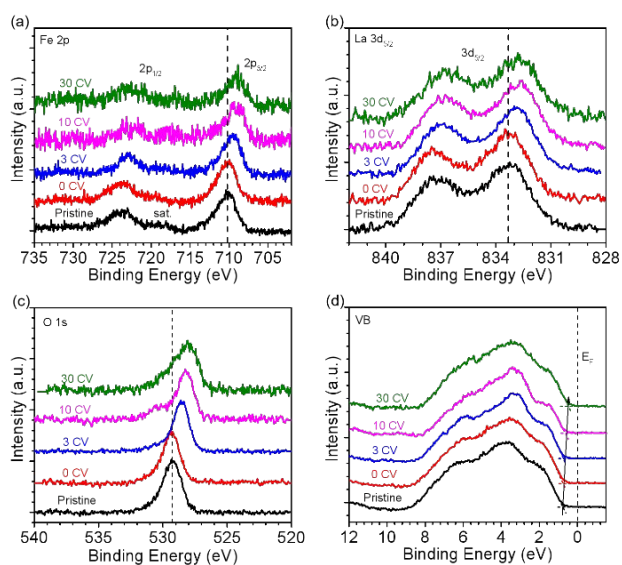


**Figure 3.** SXPS of LaFeO<sub>3</sub> with kinetic energy constant at 550 eV. (a) Fe 2p, (b) La 3d, (c) O 1s and (d) VB spectra after different CV cycles.

treatment steps, we additionally carried out synchrotron XPS (SXPS) measurements. Figure 3 shows the SXPS core level and VB spectra of LFO after different CV cycles; the XAS and XPS data have been acquired subsequently before each next OER treatment step. The Fe 2p<sub>3/2</sub> region of LFO pristine exhibits a characteristic feature located around 710.2 eV along with a satellite

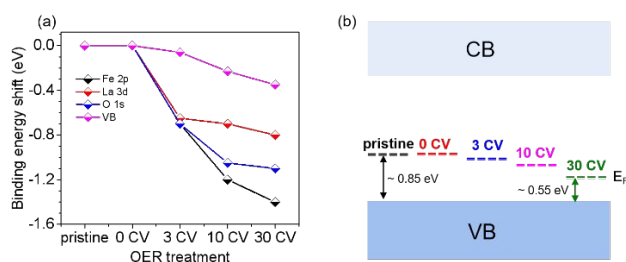

**Figure 4.** (a) Shifts of core level binding energy and (b) Fermi level (E<sub>F</sub>) position of LaFeO<sub>3</sub> relative to the VBM BE as a function of CV cycles.

peak near 719 eV, in agreement with the Fe<sup>3+</sup> oxidation state. After different OER treatments, the characteristics of Fe 2p did not change significantly, but the position of the main peak gradually shifted to lower binding energy with increasing CV cycles. The same shift is also seen in the corresponding La 3d (Figure 3b) and O 1s (Figure 3c) core level spectra. In addition, the VB

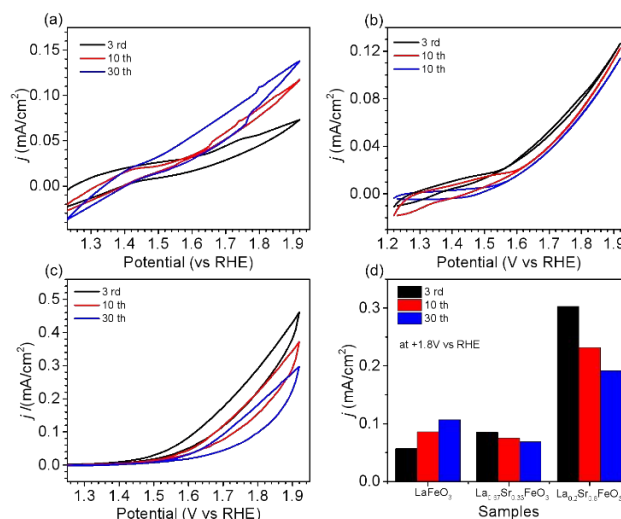

**Figure 5.** OER performance of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> with different CV cycles. (a) CV polarization curves of LaFeO<sub>3</sub>, (b) CV polarization curves of La<sub>0.67</sub>Sr<sub>0.33</sub>FeO<sub>3</sub>, (c) CV polarization curves of La<sub>0.2</sub>Sr<sub>0.8</sub>FeO<sub>3</sub> and (d) current density of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) with different CV cycles at +1.8 V (vs. RHE).

The OER performance of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> (x = 0, 0.33, 0.8) thin films were evaluated in a three-electrode setup in the double glass cross electrochemistry chamber of the SOLIAS endstation in 1 M KOH solution at 10 mV/s scan rate with a potential range of +1.22 V to +1.92 V vs RHE. The current density of CVs of all samples was normalized by the geometric area without ohmic compensation. Figure 5a shows CV plots of LFO under different CV cycles. The results suggest that the electrocatalytic activity of LFO experiences an enhancement with increasing number of CV cycles. On the contrary, the current density of LSF-0.33 (Figure 5b) as well as LSF-0.8 (Figure 5c) films show a continuous trend of decreasing OER performance. To compare the OER activity of La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub> with different Sr doping concentrations, the current densities of different samples with different CV cycles at +1.8 V (vs RHE) are shown in Figure 5d. The initial (3<sup>rd</sup> CV) OER



performance of  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  is enhanced with increasing Sr doping concentration, which is in line with our previously reported results.<sup>26</sup> More importantly, we observed a more significant decrease in OER performance for the LSF-0.8 sample compared to LSF-0.33. The current density of LSF-0.33 at +1.8 V (vs RHE) decreases from 0.085 mA/cm<sup>2</sup> (3<sup>rd</sup> CV) to 0.069 mA/cm<sup>2</sup> (30<sup>th</sup> CV), while LSF-0.8 decreases from 0.303 mA/cm<sup>2</sup> (3<sup>rd</sup> CV) to 0.192 mA/cm<sup>2</sup> (30<sup>th</sup> CV) - a reduction of 18.8% and 41.8%, respectively.


It is well known that stability is also an important metric for evaluating OER catalysts. In order to have a more in-depth understanding of OER stability of the  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  ( $x = 0, 0.33, 0.8$ ) catalysts, we calculated the compositions of La, Sr and Fe ( $\text{La}\% + \text{Sr}\% + \text{Fe}\% = 100\%$ ) from SXPS spectral region integration after different CV cycles, as shown in Table 1. There is a significant increase in La concentration on the surface of the LFO film after OER treatment, which indicated that La gradually aggregated on the surface of LFO during the OER process. Recently, She et al. reported that surface aggregation of A-site cations (La or Sr) in  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  is an important factor contributing to the poor OER

stability by blocking catalytically active sites.<sup>22</sup> In addition, we observe that the surface Sr content in both LSF-0.33 and LSF-0.8 gradually decreases with increasing CV, while the La content did not change significantly. The reduction of surface Sr concentration in LSF-0.33 and LSF-0.8 is related to the leaching of Sr during OER; a similar phenomenon has been observed in  $\text{SrIrO}_3$ .<sup>36</sup> There is a close relationship between current density and Sr concentration as shown in Figure 6. It can be clearly observed that the leaching of Sr in LSF-0.8 is particularly more pronounced as compared to LSF-0.33, in agreement with the deterioration of the OER performance.

**Table 1.** SXPS-derived (kinetic energy constant at 550 eV) La, Sr and Fe atomic compositions ( $\text{La}\% + \text{Sr}\% + \text{Fe}\% = 100\%$ ) for  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  ( $x = 0, 0.33, 0.8$ ) with different CV cycles.

	LFO		LSF-0.33			LSF-0.8		
	La	Fe	La	Sr	Fe	La	Sr	Fe
	(at. %)	(at. %)	(at. %)	(at. %)	(at. %)	(at. %)	(at. %)	(at. %)
Pristin	50.0	50.0	33.5	16.5	50.0	10.1	40.0	49.9
e <sup>a</sup>	±	±	±	±	±	±	±	±
	0.4	0.2	0.4	0.6	0.5	0.2	0.3	0.3
0 CV <sup>b</sup>	49.1	50.9	33.9	14.8	51.2	12.5	36.4	51.1
	±	±	±	±	±	±	±	±
	0.6	0.3	0.6	0.3	0.3	0.3	0.2	0.4
3 CV <sup>b</sup>	62.6	37.3	33.0	10.7	55.7	15.7	22.7	61.5
	±	±	±	±	±	±	±	±
	0.5	0.4	0.5	0.4	0.2	0.5	0.4	0.2
10 CV <sup>b</sup>	63.0	37.0	31.5	10.1	58.4	15.8	17.2	67.0
	±	±	±	±	±	±	±	±
	0.4	0.5	0.4	0.5	0.4	0.4	0.5	0.4
30 CV <sup>b</sup>	64.5	35.5	31.1	9.4	59.5	14.3	15.1	70.6
	±	±	±	±	±	±	±	±
	0.2	0.4	0.2	0.4	0.5	0.2	0.4	0.5

<sup>a</sup> Expected stoichiometry

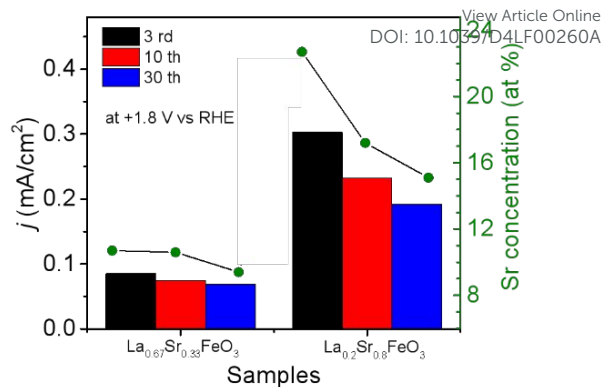

**Figure 6.** Relationship between current density and Sr concentration of  $\text{La}_{0.67}\text{Sr}_{0.33}\text{FeO}_3$  and  $\text{La}_{0.2}\text{Sr}_{0.8}\text{FeO}_3$  with different CV cycles.

<sup>b</sup> by XPS fitting

Such a different OER behaviour of  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  with CV cycling is likely attributed to two factors. The first factor is the emergence of a hole state close to the conduction band minimum. Our recent study shows that the hole state near the conduction band minimum plays a crucial role in the oxidation of water by reducing the energy barrier for electron transfer at the electrode-electrolyte interface.<sup>26</sup> The above NEXAFS O K-edge spectra of LSF-0.33 and LSF-0.8 show that the content of the hole state (~528 eV) near the conduction band gradually decreases with increasing CV cycles, resulting in a decrease of OER performance. The second factor is the occupied density of states (DOS) near the  $E_F$ . According to the Marcus-Gerischer charge transfer model,<sup>42</sup> the increase in the occupied DOS near  $E_F$  would reduce the energy of donating electrons at the electrode-electrolyte interface, which results in increased performance of the catalyst by a decrease in charge transfer overpotential. It is worth noting that our SXPS results show that the  $E_F$  of LFO is shifting toward the VBM with increasing number of CV cycles, which indicates that the occupied DOS near the  $E_F$  is gradually increasing. On the contrary, the  $E_F$  of the LSF-0.33 shift away from the VBM, resulting in a decrease of occupied DOS near the  $E_F$  of LSF-0.33. The similar trend of electrochemical activity and occupied DOS near  $E_F$  indicates that occupied DOS near  $E_F$  are an important factor for determining the OER performance. Overall, our results highlight that the OER performance of  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  ( $x = 0, 0.33, 0.8$ ) is closely related to the surface  $\text{Fe}^{4+}$  species, the hole state near the CB and the occupied DOS near the  $E_F$ . Sr leaching during OER is the key factor for the poor stability of LSF-0.33 and LSF-0.8.

## Conclusions

We have investigated the surface properties, stability of the electronic structure and OER performance of well-defined  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  ( $x = 0, 0.33, 0.8$ ) single crystal films. Our results reveal that operating the electrocatalysts under OER conditions lead to an increase of OER performance of LFO and a decrease of activity of LSF-0.33 and LSF-0.8. A combination of XRD, XRR and AFM measurements shows that the surfaces of  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$  ( $x = 0, 0.33, 0.8$ ) undergo surface morphology and compositional changes upon OER treatment. Additionally, the electronic structure also experiences significant changes especially in the concentration of  $\text{Fe}^{4+}$  oxidation state, the hole state and the position of  $E_F$  with respect to the valence band maximum. The improved activity of LFO is attributed to i) the presence of hole states as well



as ii) the increase of the occupied density of states near  $E_F$  upon OER cycling. Conversely, the reduction of these factors leads to the decrease of OER performance of LSF-0.33 and LSF-0.8. The leaching of Sr is an important factor leading to the observed poor stability of LSF-0.33 and LSF-0.8 under OER conditions, and the OER performance decays faster with increasing Sr doping concentrations at the A-site in the pristine perovskite structure. Our study provides insights into the surface structural and compositional evolution, electronic structure stability and electrochemical properties of transition metal oxides as function of OER treatment and reveals that appropriate doping has substantial impact on the OER stability of transition metal oxides. The study further demonstrates the importance of synchrotron-based investigations for the precise determination and interpretation of electrochemical properties and activities with respect to electronic structure engineering of perovskite electrocatalysts achieving optimized OER performance.

### Conflicts of interest

There are no conflicts to declare.

### Data availability

Data supporting Figures and Tables in the manuscript and the Supporting Information is made available in a ZENODO.org repository accessible under DOI:XXX.XXX.XXX (%%will be provided upon acceptance of the manuscript%%).

### Acknowledgements

Helmholtz Zentrum Berlin (HZB) is acknowledged for granting beam time at BESSY II under application 202-10001-ST-1.1-P. R. Golnak (HZB) is acknowledged for technical assistance during beam time at beamline U49-2\_PGM-1. We also thank Dr. T. Hellmann and Dr. W. Calvet for setting up SOLIAS. C. M. Tian acknowledges financial support from the China Scholarship Council (No. 202008420222). J.P. Hofmann, M. Einert, and C. Maheu acknowledge financial support from the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation under the Walter Benjamin Program to M. Einert, project no. 469377211 as well as in the priority program SPP2196, no. 423746744 and CRC 1548, FLAIR, project B07, no. 463184206).

### References

- Z. P. Izkovits, J. M. Evans, M. C. Meier, K. M. Papadantonakis and N. S. Lewis, Decoupled Electrochemical Water-splitting Systems: A Review and Perspective, *Energy Environ. Sci.*, **2021**, *14*, 4740.
- L. Schlapbach and A. Züttel, Hydrogen-Storage Materials for Mobile Applications, *Nature*, **2001**, *414*, 353-358.
- Y. Gorlin and T. F. Jaramillo, A Bifunctional Nonprecious Metal Catalyst for Oxygen Reduction and Water Oxidation, *J. Am. Chem. Soc.*, **2010**, *132*, 13612-13614.
- E. Fabbri, A. Habereder, K. Waltar, R. Kotz and T. J. Schmidt, Developments and Perspectives of Oxide-Based Catalysts for the Oxygen Evolution Reaction, *Catal. Sci. Technol.*, **2014**, *4*, 3800-3821.
- V. Petrykin, K. Macounova, O. A. Shlyakhtin and P. Krtil, Tailoring the Selectivity for Electrocatalytic Oxygen Evolution on Ruthenium Oxides by Zinc Substitution, *Angew. Chem.Int. Ed.*, **2010**, *49*,

- 4813-4815.
- Y. Lee, J. Suntivich, K. J. May, E. E. Perry and Y. Shao-Horn, Synthesis and Activities of Rutile  $\text{IrO}_2$  and  $\text{RuO}_2$  Nanoparticles for Oxygen Evolution in Acid and Alkaline Solutions, *J. Phys. Chem. Lett.*, **2012**, *3*, 399-404.
- A. Zagalskaya and V. Alexandrov, Role of Defects in the Interplay between Adsorbate Evolving and Lattice Oxygen Mechanisms of the Oxygen Evolution Reaction in  $\text{RuO}_2$  and  $\text{IrO}_2$ , *ACS Catal.*, **2020**, *10*, 3650-3657.
- N. T. Suen, S. F. Hung, Q. Quan, N. Zhang, Y. J. Xu and H. M. Chen, Electrocatalysis for the Oxygen Evolution Reaction: Recent Development and Future Perspectives, *Chem. Soc. Rev.*, **2017**, *46*, 337.
- W. T. Hong, M. Risch, K. A. Stoerzinger, A. Grimaud, J. Suntivich and Y. Shao-Horn, Toward the Rational Design of Non-Precious Transition Metal Oxides for Oxygen Electrocatalysis, *Energy Environ. Sci.*, **2015**, *8*, 1404-1427.
- K. X. Zhang and R. Q. Zou, Advanced Transition Metal-Based OER Electrocatalysts: Current Status, Opportunities, and Challenges, *Small*, **2021**, *17*, 2100129.
- D. Liu, P. F. Zhou, H. Y. Bai, H. Q. Ai, X. Y. Du, M. P. Chen, D. Liu, W. Fai, K. H. Lo, C. T. Kwok, S. Chen, S. P. Wang, G. C. Xing, X. S. Wang and H. Pan, Development of Perovskite Oxide-Based Electrocatalysts for Oxygen Evolution Reaction, *Small*, **2021**, *17*, 2101605.
- C. W. Sun, J. A. Alonso and J. J. Bian, Recent Advances in Perovskite-Type Oxides for Energy Conversion and Storage Applications, *Adv. Energy Mater.*, **2021**, *11*, 20000549.
- H. N. Sun, J. Dai, W. Zhou and Z. P. Shao, Emerging Strategies for Developing High-Performance Perovskite-Based Materials for Electrochemical Water Splitting, *Energy Fuels*, **2020**, *34*, 10547-10567.
- X. Xu, C. Su, W. Zhou, Y. Zhu, Y. Chen and Z. Shao, Co-doping Strategy for Developing Perovskite Oxides as Highly Efficient Electrocatalysts for Oxygen Evolution Reaction, *Adv. Sci.*, **2016**, *3*, 1500187.
- J. Suntivich, K. J. May, H. A. Gasteiger, J. B. Goodenough and Y. Shao-Horn, A Perovskite Oxide Optimized for Oxygen Evolution Catalysis from Molecular Orbital Principles, *Science*, **2011**, *334*, 1383-1385.
- Y. L. Lee, J. Kleis, J. Rossmeisl, Y. Shao-Horn and D. Morgan, Prediction of Solid Oxide Fuel Cell Cathode Activity With First-Principles Descriptors, *Energy Environ. Sci.*, **2011**, *4*, 3966-3970.
- J. J. Song, C. Wei, Z. F. Huang, C. T. Liu, L. Zeng, X. Wang and Z. C. J. Xu, A Review on Fundamentals for Designing Oxygen Evolution Electrocatalysts, *Chem. Soc. Rev.*, **2020**, *49*, 2196-2214.
- A. R. Burton, R. Paudel, B. Matthews, M. Sassi, S. R. Spurgeon, B. H. Farnum and R. B. Comes, Thickness Dependent OER Electrocatalysis of Epitaxial  $\text{LaFeO}_3$  Thin Films, *J. Mater. Chem. A*, **2022**, *10*, 1909-1918.
- Y. W. Dai, J. Yu, Z. B. Zhang, C. Cheng, P. Tan, Z. P. Shao and M. Ni, Interfacial La Diffusion in the  $\text{CeO}_2/\text{LaFeO}_3$  Hybrid for Enhanced Oxygen Evolution Activity, *ACS Appl. Mater. Interfaces*, **2021**, *13*, 2799-2806.
- Y. X. Li, X.Y. Zhang, Z. J. Wu, H. B. Sheng, C. Li, H. Y. Li, L. X. Cao and B. H. Dong, Coupling Porous Ni Doped  $\text{LaFeO}_3$  Nanoparticles with Amorphous  $\text{FeOOH}$  Nanosheets Yields an Interfacial Electrocatalyst for Electrocatalytic Oxygen Evolution, *J. Mater. Chem. A*, **2021**, *9*, 23545-23554.
- J. Dai, Y. L. Zhu, Y. J. Zhong, J. Miao, B. W. Lin, W. Zhou and Z. P. Song,



- Enabling High and Stable Electrocatalytic Activity of Iron-Based Perovskite Oxides for Water Splitting by Combined Bulk Doping and Morphology Designing, *Adv. Mater. Interfaces*, **2019**, *6*, 1801317.
22. S. X. She, J. Yu, W. Q. Tang, Y. L. Zhu, Y. B. Chen, J. Sunarso, W. Zhou and Z. P. Shao, Systematic Study of Oxygen Evolution Activity and Stability on  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_{3-6}$  Perovskite Electrocatalysts in Alkaline Media, *ACS Appl. Mater. Interfaces*, **2018**, *10*, 11715–11721.
  23. Z. S. Li, L. Lv, J. S. Wang, X. Ao, Y. J. Ruan, D. Z. Zha, G. Hong, Q. H. Wu, Y. C. Lan, C. D. Wang, J. J. Jiang and M. L. Liu, Engineering Phosphorus-doped  $\text{LaFeO}_{3-6}$  Perovskite Oxide as Robust Bifunctional Oxygen Electrocatalysts in Alkaline Solutions, *Nano Energy*, **2018**, *47*, 199–209.
  24. P. Shikha, T. S. Kang and B. S. Randhawa, Effect of Different Synthetic Routes on the Structural, Morphological and Magnetic Properties of Ce Doped  $\text{LaFeO}_3$  Nanoparticles, *J. Alloys Compd.*, **2015**, *625*, 336–345.
  25. R. A. Rincón, E. Ventosa, F. Tietz, J. Masa, S. Seisel, V. Kuznetsov and W. Schuhmann, Evaluation of Perovskites as Electrocatalysts for the Oxygen Evolution Reaction, *ChemPhysChem*, **2014**, *15*, 2810 – 2816.
  26. Z. C. Shen, Y. B. Zhuang, W. W. Li, X. C. Huang, F. E. Oropeza, E. J. M. Hensen, J. P. Hofmann, M. Y. Cui, A. Tadich, D. C. Qi, J. Cheng, J. Li and K. H. L. Zhang, Increased Activity in the Oxygen Evolution Reaction by  $\text{Fe}^{4+}$ -induced Hole States in Perovskite  $\text{La}_{1-x}\text{Sr}_x\text{FeO}_3$ , *J. Mater. Chem. A*, **2020**, *8*, 4407–4415.
  27. P. P. Lopes, D. Y. Chung, X. Rui, H. Zheng, H. Y. He, P. F. B. D. Martins, D. Strmcnik, V. R. Stamenkovic, P. Zapol, J. F. Mitchell, R. F. Klie and N. M. Markovic, Dynamically Stable Active Sites from Surface Evolution of Perovskite Materials during the Oxygen Evolution Reaction, *J. Am. Chem. Soc.*, **2021**, *143*, 2741–2750.
  28. J. J. Suo, B. W. Yang, E. Mosconi, H. S. Choi, Y. J. Kim, S. M. Zakeeruddin, F. D. Angelis, M. Grätzel, H. S. Kim and A. Hagfeldt, Surface Reconstruction Engineering with Synergistic Effect of Mixed-Salt Passivation Treatment Toward Efficient and Stable Perovskite Solar Cells, *Adv. Funct. Mater.*, **2021**, *31*, 2102902.
  29. Y. Sun, R. Li, X. X. Chen, J. Wu, Y. Xie, X. Wang, K. K. Ma, L. Wang, Z. Zhang, Q. L. Liao, Z. Kang and Y. Zhang, A-Site Management Prompts the Dynamic Reconstructed Active Phase of Perovskite Oxide OER Catalysts, *Adv. Energy Mater.*, **2021**, *11*, 2003755.
  30. L. K. Gao, X. Cui, C. D. Sewell, J. Li and Z. Q. Lin, Recent Advances in Activating Surface Reconstruction for the High-Efficiency Oxygen Evolution Reaction, *Chem. Soc. Rev.*, **2021**, *50*, 8428.
  31. A. Grimaud, A. Demortiere, M. Saubanere, W. Dachraoui, M. Duchamp, M. L. Doublet and J. M. Tarascon, Activation of Surface Oxygen Sites on an Iridium-Based Model Catalyst for the Oxygen Evolution Reaction, *Nat. Energy*, **2016**, *2*, 1–10.
  32. Y. Sun, C. R. Wu, T. Y. Ding, J. Gu, J. W. Yang, J. Cheng and K. H. L. Zhang, Direct Observation of the Dynamic Reconstructed Active Phase of Perovskite  $\text{LaNiO}_3$  for the Oxygen-Evolution Reaction, *Chem. Sci.*, **2023**, *14*, 5906–5911.
  33. M. J. Choi, L. Wang, K. A. Stoerzinger, S. Y. Chung, S. A. Chambers and Y. G. Du, Epitaxial Design of Complex Nickelates as Electrocatalysts for the Oxygen Evolution Reaction, *Adv. Energy Mater.*, **2023**, *13*, 2300239.
  34. E. M. Kiens, M. J. Choi, L. H. Wei, Q. Y. Lu, L. Wang and C. Baeumer, Deeper Mechanistic Insights into Epitaxial Nickelate Electrocatalysts for the Oxygen Evolution Reaction, *Chem. Commun.*, **2023**, *59*, 4562–4577.
  35. Y. Y. Li, X. C. Du, J. W. Huang, C. Y. Wu, Y. H. Sun, G. P. Zhou, C. P. Yang and J. Xiong, Recent Progress on Surface Reconstruction of Earth-Abundant Electrocatalysts for Water Oxidation, *Small*, **2019**, *15*, 1901980.
  36. G. Wan, J. W. Freeland, J. Kloppenburg, G. Petretto, J. N. Nelson, D. Y. Kuo, C. J. Sun, J. G. Wen, J. T. Diulus, G. S. Herman, Y. Q. Dong, R. H. Kou, J. Y. Sun, S. Chen, K. M. Shen, D. G. Schlom, G. M. Rignanese, G. Hautier, D. D. Fong, Z. X. Feng, H. Zhou and J. Suntivich, Amorphization Mechanism of  $\text{SrIrO}_3$  Electrocatalyst: How Oxygen Redox Initiates Ionic Diffusion and Structural Reorganization, *Sci. Adv.*, **2021**, *7*, 7323.
  37. E. Fabbri, M. Nachtegaal, T. Binniger, X. Cheng, B. J. Kim, J. Durst, F. Bozza, T. Graule, R. Schäublin, L. Wiles, M. Pertoso, N. Danilovic, K. E. Ayers and T. J. Schmidt, Dynamic Surface Self-Reconstruction is the Key of Highly Active Perovskite Nano-Electrocatalysts for Water Splitting, *Nat. Mater.*, **2017**, *16*, 925–931.
  38. T. Mayer, M. Lebedev, R. Hunger and W. Jaegermann, Elementary Processes at Semiconductor/Electrolyte Interfaces: Perspectives and Limits of Electron Spectroscopy, *Appl. Surf. Sci.*, **2005**, *252*, 31–42.
  39. S. J. Callori, S. Hu, J. Bertinshaw, Z. J. Yue, S. Danilkin, X. L. Wang, V. Nagarajan, F. Klose, J. Seidel and C. Ulrich, Strain-Induced Magnetic Phase Transition in  $\text{SrCoO}_{3-6}$  Thin Films, *Phys. Rev. B*, **2015**, *91*, 140405.
  40. S. Roh, S. Lee, M. Lee, Y. S. Seo, A. Khare, T. Yoo, S. Woo, W. S. Choi and J. Hwang, Oxygen Vacancy Induced Structural Evolution of  $\text{SrFeO}_{3-x}$  Epitaxial Thin Film from Brownmillerite to Perovskite, *Phys. Rev. B*, **2018**, *97*, 075104.
  41. H. Liu, R. R. Xie, Q. X. Wang, J. L. Han, Y. Han, J. Wang, H. Fang, J. Qi, M. Ding, W. X. Ji, B. He, W. M. Lü, Enhanced OER Performance and Dynamic Transition of Surface Reconstruction in  $\text{LaNiO}_3$  Thin Films with Nanoparticles Decoration, *Adv. Sci.*, **2023**, 2207128.
  42. I. Heller, J. Kong, K. A. Williams, C. Dekker and S. G. Lemay, Electrochemistry at Single-Walled Carbon Nanotubes: The Role of Band Structure and Quantum Capacitance, *J. Am. Chem. Soc.*, **2006**, *128*, 7353–7359.

View Article Online

DOI: 10.1039/D1CY00360A





View Article Online  
DOI: 10.1039/D4LF00260A

### Data availability

Data supporting Figures and Tables in the manuscript and the Supporting Information is made available in a ZENODO.org repository accessible under DOI:XXX.XXX.XXX (%%will be provided upon acceptance of the manuscript%%).

