



Green  
Chemistry

**A rapid electrochemical method to recycle carbon fiber  
composites using methyl radicals**

|                               |  |
|-------------------------------|--|
| Journal:                      | <i>Green Chemistry</i>   |
| Manuscript ID                 | GC-COM-05-2023-001765.R1   |
| Article Type:                 | Communication  |
| Date Submitted by the Author: | 10-Jul-2023  |
| Complete List of Authors:     | Yu, Zehan; University of Southern California, MC Gill Composites Center; University of Southern California, M.C.Gill Composite Center<br>Lim, Y.; University of Southern California, Department of Chemistry<br>Williams, Travis; University of Southern California, Loker Hydrocarbon Research Institute<br>Nutt, Steven; University of Southern California, Department of Chemical Engineering and Materials Science MC Gill Composites Center |
|                               |  |

SCHOLARONE™  
Manuscripts

## COMMUNICATION

## A rapid electrochemical method to recycle carbon fiber composites using methyl radicals

Zehan Yu<sup>a,c</sup>, Y. Justin Lim<sup>b,c</sup>, Travis Williams<sup>b,\*</sup>, and Steven Nutt<sup>a,\*</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx


DOI: 10.1039/x0xx00000x

**We introduce an electrochemical approach to recycle carbon fiber (CF) fabrics from amine-epoxy carbon fiber-reinforced polymers (CFRPs). Our novel method utilizes a Kolbe-like mechanism to generate methyl radicals from CH<sub>3</sub>COOH to cleave C-N bonds within epoxy matrices via hydrogen atom abstraction. Recovered CFs are then remanufactured into CFRPs without resizing.**

Thermoset carbon fiber reinforced polymer (CFRP) composites comprise a polymer matrix and carbon fibers (CFs) so that the combination imparts exceptional strength-to-weight, stiffness, and corrosion resistance relative to metallic alloys. Because of these properties, CFRPs are top choices for lightweight structural components in the aerospace, automobile, and wind energy industries. There has been a continuous increase in global demand for CFRPs, projected to reach 285,000 tons in 2025.<sup>1</sup> Thermoset CFRPs are cured irreversibly to produce a solid, crosslinked polymer matrix. Once the process completes, the matrix is insoluble and inert. Thus, recycling end-of-life (EOL) CFRPs is challenging.

We have previously introduced oxidative recycling processes for benzoxazine and amine-epoxy CFRPs, respectively based on ruthenium hydride abstraction<sup>2</sup> and peroxide<sup>3</sup> or O<sub>2</sub>/Mn<sup>II</sup> conditions,<sup>4</sup> each enabling both fiber and resin recovery and featuring analysis of chemical mechanism (Scheme 1a).<sup>5</sup> Building on these insights, we now present the first electrochemical method to deploy electrolysis-generated methyl radicals to depolymerize amine-epoxy CFRPs (Scheme 1). In this process, we use fibers imbedded within the CFRP as the anode to electrolyze CH<sub>3</sub>COOH and generate methyl radicals

directly on the CFRP. Such radicals abstract hydrogen atoms adjacent to the polymer's linking nitrogen atom, thus, ultimately enabling selective C-N bond cleavage and completely dissolving CFRP matrices (T<sub>g</sub> > 160°C) within 20 hours while preserving the fabric architecture of CFs. Fiber fabrics were then directly remanufactured to produce second-cycle CFRPs.

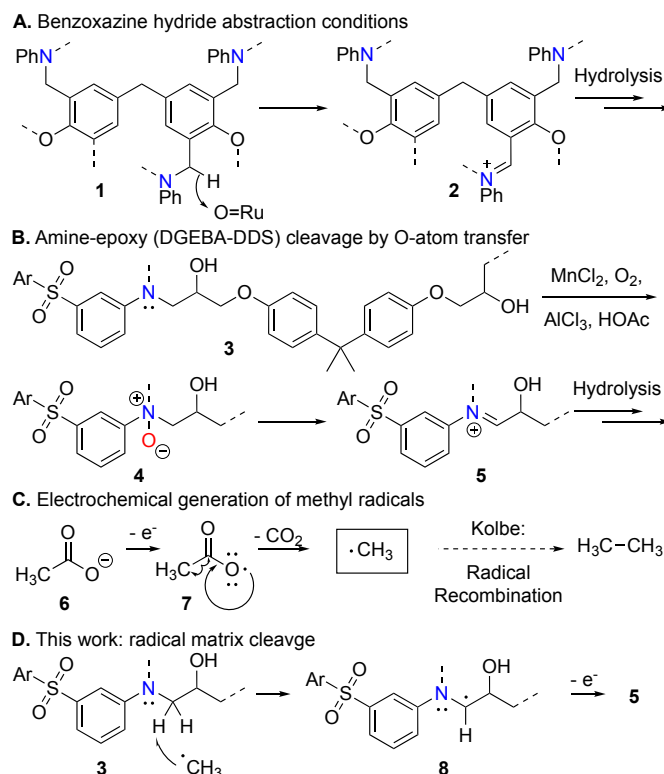

**Scheme 1** Approaches to cleave various CFRP matrices.


<sup>a, a</sup>MC Gill Composites Center, Mork Family Department of Chemical Engineering and Material Science, University of Southern California, 3651 Watt Way, Los Angeles, California, 90089, USA.

<sup>b, b</sup>Loker Hydrocarbon Research Institute, Wrigley Institute of Environmental Studies, and Department of Chemistry, University of Southern California, 837 Bloom Walk, Los Angeles, California, 90089, USA.

<sup>c, c</sup>Co-first author.

<sup>d, \*</sup>Co-corresponding author.

† Electronic Supplementary Information (ESI) available

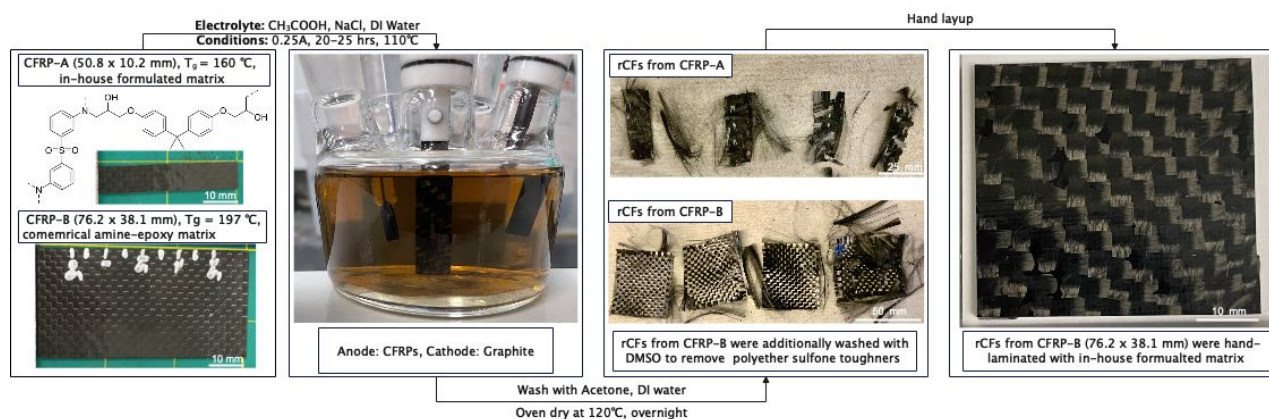

**Scheme 2** Electrolysis recycling process for recovering and reusing CFs from amine-epoxy CFRPs

Electrochemical approaches to CFRP recycling have emerged that attempt to leverage the conductive CFs present in the composites. Currently, most electrochemical recycling methods use a CFRP as the anode to electrolyze chloride solutions. These methods reportedly generate chlorine-based oxidants (Cl<sub>2</sub>, HOCl, -OCl) that degrade thermoset polymers and can also chlorinate imbedded fibers.<sup>6-8</sup> Alternative chlorine-free electrochemical methods involve phosphoric acid or a mixture of dimethyl sulfoxide (DMSO) and ammonium acetate.<sup>9, 10</sup> These methods have lower efficiency, taking up to 21 days to complete, and tend to damage the fibers.

Additionally, to our view, no satisfying mechanistic data have been reported on any electrochemical CFRP digest method. Previous studies have shown that photolysis-generated chlorine and hydroxyl radicals digest organic waste.<sup>11</sup> Some CFRP recycling studies have proposed to use radical-based reaction mechanisms to achieve efficient matrix digestion.<sup>12-15</sup> However, these studies did not characterize the reactive intermediate(s) or pathway of depolymerization. Here we will use a spin trap strategy to obtain structural information on our propagating radical(s).

Our method is based on a Kolbe-like electrolysis that generates methyl radicals to cleave C—H groups in an amine-epoxy matrix. Thus, acetic acid decomposes to methyl radicals as shown in Scheme 1c.<sup>16</sup> This happens on the carbon fiber electrode imbedded within the CFRP material. The transient radical mediates a curiously selective hydrogen atom abstraction, ultimately converting the matrix's linking amine to a hydrolysable imine (Scheme 1d).

We demonstrate this concept with two CFRPs, A and B, prepared with different amine-epoxy matrices (see ESI for details). CFRP-A (T<sub>g</sub> = 160 °C) was produced in-house using diglycidyl ether of bisphenol A (DGEBA) epoxy and 3,3'-diaminodiphenyl sulfone (3,3'-DDS), as in Scheme 1b. CFRP-B samples (T<sub>g</sub> = 197 °C) were produced using a commercial prepreg of a similar structure (Solvay CYCOM 5320-1) to demonstrate the feasibility of recovering materials from an aerospace material.

Once fully cured, CFRPs laminates were cut to 50.8 x 10.2 or 76.2 x 38.1 mm for use as the anode, while a graphite rod served as the cathode (Scheme 2). The electrodes were immersed in an electrolyte solution containing CH<sub>3</sub>COOH, NaCl, and deionized

water. Added NaCl assists electron transportation and enhance the conductivity of electrolyte solutions. Electrolysis reactions were performed at constant current (0.25 A) at 110 °C for 20 hours under reflux with various electrolyte concentrations, respectively summarized in Table 1. Entries 1-7 test the effect of NaCl and CH<sub>3</sub>COOH. Entry 8 and 9 demonstrate feasibility of the method on our commercial CFRPs.

**Table 1** Electrolysis CFRP digestion experiment summary

| Entry | CFRP                    | CH <sub>3</sub> COOH(M) | NaCl(M) |
|-------|-------------------------|-------------------------|---------|
| 1     | CFRP-A (50.8 x 10.2 mm) | 1.93                    | 1       |
| 2     | CFRP-A (50.8 x 10.2 mm) | 4.35                    | 1       |
| 3     | CFRP-A (50.8 x 10.2 mm) | 6.77                    | 1       |
| 4     | CFRP-A (50.8 x 10.2 mm) | 8.70                    | 1       |
| 5     | CFRP-A (50.8 x 10.2 mm) | 11.6                    | 1       |
| 6     | CFRP-A (50.8 x 10.2 mm) | 11.6                    | 0.75    |
| 7     | CFRP-A (50.8 x 10.2 mm) | 11.6                    | 0.5     |
| 8     | CFRP-B (50.8 x 10.2 mm) | 11.6                    | 1       |
| 9     | CFRP-B (76.2 x 38.1 mm) | 11.6                    | 1       |

Clean CF fabrics are recovered after electrolysis. Figure 1 shows light microscope images of fabrics recovered after 20 hours using conditions in Table 1. Images of entries 1-5 show more complete matrix removal with increasing CH<sub>3</sub>COOH concentration (1.93-11.6 M) at constant NaCl concentration (1 M). Images of entries 5-8 reveal that increasing NaCl concentration (0.5-1M) resulted in more complete matrix decomposition at constant CH<sub>3</sub>COOH concentration (11.6 M). These show that higher [CH<sub>3</sub>COOH] and [NaCl] reduced digestion times. Therefore, we chose 11.6 M CH<sub>3</sub>COOH and 1 M NaCl (entries 5, 7 and 8).

Figure S2 shows the measured voltage of Table 1, entry 5 fluctuated between 4-6.5 V during the electrolysis. Thus, 4 V was selected as optimal, and we switched conditions to fixed voltage.


Single fiber tensile strengths of fresh and recovered CFs were measured and summarized in Table S2 (see ESI for details). The results show reclaimed CFs retained 94.24% of tensile strength and 83.43% of modulus.

Figure 2 shows SEM images of virgin CF and recovered CFs from entries 5 and 8. Figure 2(a) shows surface grooves



**Figure 1** Optical microscope images of recycled CFs from entries 1-8, remaining resin residues (white arrows)

by < 0.8 wt%, indicating no evidence of oxidation or chlorination on recovered CFs. An alternative electrolysis recycling method that involved chlorine reported surface chlorine content increased by up to 8 wt%.<sup>6</sup> The difference in surface chemistry implies that the active radical in our system is carbon-centered, not chlorine or oxygen, as implied elsewhere.

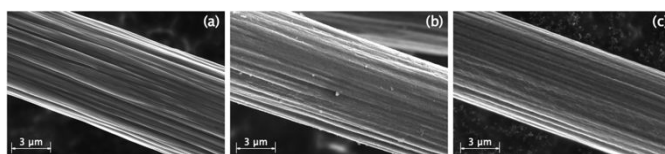

**Figure 2** SEM images of virgin CF (a) and recycled CFs from entries 5 (b) and 8 (c)

**Table 2** EDS surface element composition analysis summary

| Sample      | C (wt%) | N (wt%) | O (wt%) |
|-------------|---------|---------|---------|
| Virgin CF   | 92.3    | 6.8     | 0.9     |
| Recycled CF | 93.8    | 4.5     | 1.7     |

Scheme 2 also illustrates the process of recovering CF sheets from CFRP-B and remanufacturing them into second cycle CFRPs. First, CFRP-B (76.2 x 38.1 mm) samples were electrolyzed for 25 hours under optimized conditions. Recovered CF fabrics were washed successively with acetone, deionized water, and DMSO to remove excess reactants and polyether sulfone tougheners. After drying, cleaned fabrics were hand-laminated with in-house resin (as in CFRP-A). Remanufactured CFRPs were fully consolidated, demonstrating the viability of up-cycling intact CF fabric from electrolysis conditions.

We next attempted to spin trap our active radical. This utilizes a nitron spin trap to react with any present radicals and produce a long-lived adduct that can be analyzed by EPR and MS.<sup>17</sup> 5,5-dimethyl-1-pyrroline-*N*-oxide (DMPO) was used to capture and identify radicals. Radicals were generated in the presence and absence of matrix, the latter involving an experiment with a bare CF sheet. Finally, a representative surrogate of the matrix (Bu<sub>4</sub>DDS) was used to confirm that C-N bonds were the cleavage sites.

We first confirmed radical generation. Table 3 shows two trials with the spin trap DMPO using bare fiber (entry A1 and CFRP-A (entry A2) as the anode. EPR confirmed the presence of new radical adducts (Figure S7). Next, we compared the rates of conversion between entries A1 and A2. A sample of each entry was collected after 1 h electrolysis and analyzed by NMR. Despite paramagnetism of the nitroxide radical, structural details of DMPO ring were detectable. Figure S9 shows comparison of the nitron signals in (a) pure DMPO, (b) entry A1, and (c) entry A2. The nitron signal at  $\delta = 7.5$  ppm remains in entry A1 but not A2, indicating that the presence of matrix greatly reduces the rate of conversion of DMPO. Thus, the radical is constrained around the matrix. This is supported by COSY NMR data, which also show no nitron signal for entry A2 (Figure S10).


**Table 3** Active radical trapping experiment summary

| Entry | Electrolysis conditions                    | Spin trap | Anode  | Sampling time |
|-------|--|-----------|--------|---------------|
| A1    | CH <sub>3</sub> COOH (11.6M), NaCl (1M)    | DMPO      | CFs    | 1hr           |
| A2    | CH <sub>3</sub> COOH (11.6M), NaCl (0.75M) |           | CFRP-A |               |

To identify the propagating radical itself, a sample of entry A1 was analyzed by MS and showed three strong signals at  $m/z = 130$ , 172, and 194, as illustrated in Figure 3. Positive control experiments were established for the methyl, hydroxyl, and chlorine DMPO radical adducts.

**Table 4** LC-QTOF assignment and positive control experiment

| Entry | Conditions  | Spin trap | Adduct ( $m/z$ ) |
|-------|---|-----------|------------------|
| C1    | C <sub>8</sub> H <sub>18</sub> O <sub>2</sub> (DTBP)                                  | DMPO      | 130              |
| C2    | CuCl <sub>2</sub> , Hepes, H <sub>2</sub> O <sub>2</sub>                              |           | 131              |
| C3    | C <sub>8</sub> H <sub>12</sub> N <sub>4</sub> (AIBN), SO <sub>2</sub> Cl <sub>2</sub> |           | 148,149,150,151  |

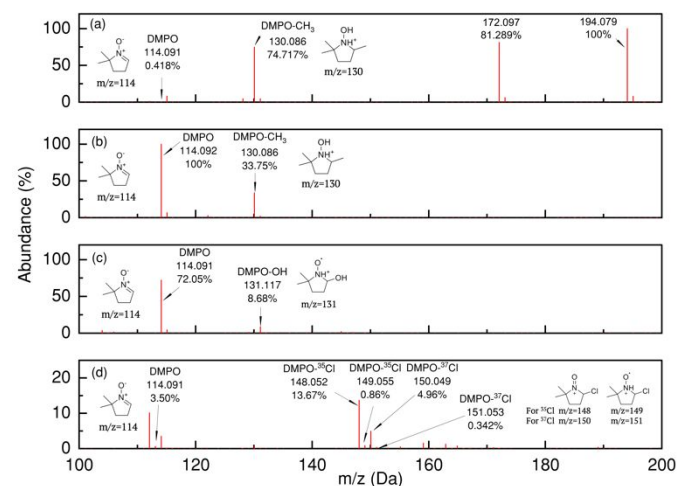

**Figure 3** LC-QTOF spectrum of entry A1 (a), C1 (b), C2 (c), and C3 (d). Only entries A1 and C1 display a strong signal for  $m/z = 130$ , which confirms the production of methyl radicals.

Using conditions shown in Table 4. Entry C1-3 respectively produced methyl, hydroxyl, and chlorine radicals that were respectively trapped cleanly by DMPO. Figure 3 further shows the stacked mass data for each trapped radical species,

including CFRP experiment A1. The signal  $m/z=130$  from A1 aligns only with the methyl radical adduct C1. The finding of methyl radicals is further supported by GC headspace analysis of experiment A1. This exhibits both methane and carbon dioxide (Figure S15), which is consistent with the formation of a methyl radical through a Kolbe-like process (Scheme 1C).

We further identified the site of matrix cleavage by using Bu<sub>4</sub>DDS, a small molecule model of the matrix (Figure S16). Thus, Bu<sub>4</sub>DDS was exposed to our electrolysis system for two hours, using a bare carbon fiber fabric anode. NMR tracked molecular changes; these conditions are laid out in Table 5 and Figure S17. We note a decrease in a signal at  $\delta = 3.29$ , which is characteristic of the R<sub>2</sub>N-CH<sub>2</sub>R group. The corresponding appearance of a  $\delta = 2.98$  signal represents mono-dealkylated Bu<sub>3</sub>DDS and N,N'-Bu<sub>2</sub>DDS. We surmise that these form via C—H atom abstraction, followed by oxidation to an iminium cation that hydrolyzes readily. Interestingly, while dealkylation proceeds all the way to primary anilines, no further degradation is observed. This was proven when we attempted to digest DDS and isolated unreacted DDS and acetylated DDS derivatives, the latter acetylated by the solvent (Figure S18 and S19).

**Table 5** Bu<sub>4</sub>DDS small molecule matrix model digestion experiment summary

| Entry | Electrolysis conditions       | Matrix              | Anode    | Sampling time |
|-------|-------------------------------|---------------------|----------|---------------|
| B1    | CH <sub>3</sub> COOH (11.6M), | Bu <sub>4</sub> DDS | Graphite | 1hr           |
| B2    | NaCl (1M) 4V,60°C             |                     |          | 2hr           |

Our combined data lead to a proposed mechanism for this process, shown in Scheme 1D. Methyl radicals are the active oxidant in the system, cleaving the R<sub>2</sub>N-CH<sub>2</sub>R bond by an initial hydrogen atom abstraction. This leads to iminium hydrolysis and selective bond cleavage at the polymeric C—N linkage.

In summary, we report an efficient electrochemical CRFP recycling method. Careful mechanistic studies hold that the process exploits methyl radicals, derived from solvent electrooxidation, selectively to depolymerize amine-epoxy matrices to form recoverable fine chemicals. Unlike prior electrochemical methods, this radical-based technology achieves complete dissolution of high-performance CFRPs within 20 hours and yields clean CFs that are readily remanufactured into second-generation CFRPs. We confirm the presence of methyl radicals with the first application of spin trapping methodology in CRFP recycling. The study provides a new chemical recycling pathway using radicals to up-cycle high-performance composites.

## Conflicts of interest

Williams is the founder of Closed Composites, a start-up aiming to commercialize composite materials recycling.

## Acknowledgement

This work is sponsored by the MC Gill Composites Center at USC and the National Science Foundation (CMMI-2134658). and

TJW thanks NSF for BRITE award sponsorship (CMMI-2227649). We thank the NSF (CHE-2018740, DBI-0821671, CHE-0840366), the NIH (S10 RR25432), and USC Research and Innovation Instrumentation Awards for analytical tools. Huntsman Corporation and Solvay generously donated the epoxy, amine curing agent, and prepreg used in this study. We thank Brian Feng for taking SEM and EDS characterization and Jaideep Singh for EPR characterization.

## Notes and references

- J. Zhang, G. Lin, U. Vaidya and H. Wang, *Composites Part B: Engineering*, 2022, 110463.
- J. N. Lo, S. R. Nutt and T. J. Williams, *ACS Sustainable Chemistry & Engineering*, 2018, **6**, 7227-7231.
- Y. Ma, D. Kim and S. R. Nutt, *Polymer Degradation and Stability*, 2017, **146**, 240-249.
- C. A. Navarro, Y. Ma, K. H. Michael, H. M. Breunig, S. R. Nutt and T. J. Williams, *Green Chemistry*, 2021, **23**, 6356-6360.
- C. A. Navarro, E. A. Kedzie, Y. Ma, K. H. Michael, S. R. Nutt and T. J. Williams, *Topics in Catalysis*, 2018, **61**, 704-709.
- H. Sun, G. Guo, S. A. Memon, W. Xu, Q. Zhang, J.-H. Zhu and F. Xing, *Composites Part A: Applied Science and Manufacturing*, 2015, **78**, 10-17.
- J.-H. Zhu, P.-Y. Chen, M.-N. Su, C. Pei and F. Xing, *Green Chemistry*, 2019, **21**, 1635-1647.
- K. Oshima, S. Matsuda, M. Hosaka and S. Satokawa, *Separation and Purification Technology*, 2020, **231**, 115885.
- K. Oshima, M. Hosaka, S. Matsuda and S. Satokawa, *Separation and Purification Technology*, 2020, **251**, 117296.
- C. Pei, P.-Y. Chen, S.-C. Kong, J. Wu, J.-H. Zhu and F. Xing, *Separation and Purification Technology*, 2021, **278**, 119591.
- S. Xiao, J. Qu, X. Zhao, H. Liu and D. Wan, *Water Research*, 2009, **43**, 1432-1440.
- M. Das, R. Chacko and S. Varughese, *ACS Sustainable Chemistry & Engineering*, 2018, **6**, 1564-1571.
- A. Yu, Y. Hong, E. Song, H. Kim, I. Choi and M. Goh, *Journal of Industrial and Engineering Chemistry*, 2022, **112**, 193-200.
- D. H. Kim, M. Lee and M. Goh, *ACS Sustainable Chemistry & Engineering*, 2020, **8**, 2433-2440.
- M. Lee, D. H. Kim, J.-J. Park, N.-H. You and M. Goh, *Waste Management*, 2020, **118**, 190-196.
- F. J. Holzhäuser, J. B. Mensah and R. Palkovits, *Green Chemistry*, 2020, **22**, 286-301.
- M. J. Davies, *Methods*, 2016, **109**, 21-30.