

Cite this: *Nanoscale*, 2023, 15, 18999

# A supramolecular assembly-based strategy towards the generation and amplification of photon up-conversion and circularly polarized luminescence

Alisha Sengupta, Gargee Roy, Aakash Ravikant Likhari and Deepak Asthana \*

For the molecular properties in which energy transfer/migration is determinantal, such as triplet–triplet annihilation-based photon up-conversion (TTAUC), the overall performance is largely affected by the intermolecular distance and relative molecular orientations. In such scenarios, tools that may steer the intermolecular interactions and provide control over molecular organisation in the bulk, become most valuable. Often these non-covalent interactions, found predominantly in supramolecular assemblies, enable pre-programming of the molecular network in the assembled structures. In other words, by employing supramolecular chemistry principles, an arrangement where molecular units are arranged in a desired fashion, very much like a Lego toy, could be achieved. This leads to enhanced energy transfer from one molecule to other. In recent past, chiral luminescent systems have attracted huge attention for producing circularly polarized luminescence (CPL). In such systems, chirality is a necessary requirement. Chirality induction/transfer through supramolecular interactions has been known for a long time. It was realized recently that it may help in the generation and amplification of CPL signals as well. In this review article we have discussed the applicability of self-/co-assembly processes for achieving maximum TTA-UC and CPL in various molecular systems.

Received 21st August 2023,  
Accepted 7th November 2023  
DOI: 10.1039/d3nr04184k

rs.c.li/nanoscale

## 1. Introduction

Supramolecular systems, found ubiquitously in nature, are networks of molecules in which many molecular units are joined

together to form nano-architectures with distinctive sizes and shapes. Glues that keep molecular building blocks held within the structure are weak noncovalent intermolecular interactions like hydrogen bonding,  $\pi$ - $\pi$  stacking, dipolar interactions, van der Waals forces, hydrophobicity, *etc.* Despite being much weaker than any regular covalent bonds, such interactions control the realms of supramolecular chemistry. Molecules could be designed to fulfil any functional requirement, for

Department of Chemistry, Ashoka University, Sonapat, Haryana 131029, India.  
E-mail: deepak.asthana@ashoka.edu.in



**Alisha Sengupta**

*Alisha Sengupta has completed her B.Sc. and M.Sc. degrees in chemistry from Jadavpur University, Kolkata, India. Currently she is a Ph.D. scholar at Ashoka University. Her current research interests include design and synthesis of luminescent supramolecular/macrocyclic systems that are suitable for biological applications and display triplet-triplet annihilation-based photon up-conversion (TTA-UC).*



**Gargee Roy**

*Gargee Roy is currently pursuing her Ph.D. degree in Materials Chemistry from Ashoka University, India. She has completed her B.Sc. (Chemistry) and M.Sc. (Inorganic Chemistry) degrees from University of Calcutta, India. Her research interests include supramolecular chemistry, electroactive materials, and molecular cages.*

example, they could be tuned to function as a molecular recognition unit, a receptor, an ion transporter *etc.*, and for this reason, supramolecular chemistry has been described as “the designed chemistry of the intermolecular bond”.<sup>1</sup> These forces are determinantal in many natural processes including photosynthesis, and are responsible for specific structures of proteins and DNA double helix formation.<sup>2</sup> In some cases, the structural features of monomer building units are overwhelmingly restrictive and require a great amount of flexibility to establish intermolecular interactions. Weak noncovalent interactions discussed above can be effective over a significantly long range of distances and orientations. For example, hydrogen bonds (H-bonds) can vary from 2.5 Å to 3.0 Å in length and from 90° to 180° in angle.<sup>3</sup> A new class of porous supramolecular systems, also known as hydrogen-bonded organic frameworks (HOFs), is one such example where hydrogen bonding and  $\pi$ - $\pi$  stacking interactions play crucial roles.<sup>4,5</sup>

The unique feature that supramolecular networks have to offer is the retention of individual molecules' identity in the assembled network. This implies that specific applications where the molecular arrangement in the bulk is a prerequisite, for example, light harvesting, molecular recognition, drug delivery systems, molecular motors, molecular devices, *etc.*, self-assembly could be of great importance.<sup>6-20</sup> A large number of examples are available in the literature where supramolecular interactions have been used to control the molecular organisation in the bulk.<sup>21,22</sup> An interesting collection of reviews discussing the progress in various fields of supramolecular chemistry was published in 2017 to celebrate the fiftieth anniversary of C. J. Pedersen's landmark work on metal ion-crown ether complexes.<sup>23</sup>

The supramolecular approach provides a unique way to modify some of the most desirable features of a molecular system, including excited state properties.<sup>24-27</sup> Supramolecular platforms have been widely used to widen the range over which energy could be transferred.<sup>28</sup> Inspiration comes directly from a natural light harvesting process in which long range energy transfer plays a key role. As we know that Dexter and Förster types of energy transfer processes have an intermolecular distance dependency, the molecular arrangement becomes a deciding factor.<sup>29</sup> For the Dexter-type energy transfer to take place, donor (D) and acceptor (A) molecules must be within 1 nm of distance, whereas, the Förster-type energy transfer can take place at much longer distances ( $\leq 10$  nm). This implies that the efficiency of energy transfer could be fine-tuned to reach the maximum amount by controlling the molecular organization in the bulk. In fact, a supramolecular self-/co-assembly tool has been frequently used to modulate the overall energy transfers and/or to manipulate the optical properties of the material.<sup>30</sup>

During the self-assembly process, the intermolecular distances reduce significantly which has a huge impact on the energy transfer processes. A judicious design of building blocks may lead to the formation of a desired molecular network allowing the manipulation of energy transfers in the bulk. This has found huge application in designing triplet-triplet annihilation-based photon up-conversion (TTA-UC).<sup>31-37</sup> A prerequisite for this to happen is a specific arrangement of a chromophore that may allow the Dexter-type energy transfer.<sup>38</sup>

Self-assembly has been extremely useful in the fields of photonics where a bottom-up approach has been used to obtain photonic crystals or to create nanoparticle arrays for a



**Aakash Ravikant Likhar**

*Aakash Ravikant Likhar completed his B.Sc. studies from Ambedkar College, Nagpur and M.Sc. from Sir Parashurambhau College, Pune, India. Currently he is a Ph.D. student and his doctoral research at Ashoka University is about the synthesis of multi-chromophoric materials for multi-modal circularly polarized luminescence.*



**Deepak Asthana**

*Dr Deepak Asthana obtained his Ph.D. degree in Supramolecular and Materials chemistry from the School of Physical Sciences, Jawaharlal Nehru University, New Delhi, India. He was awarded JSPS postdoctoral fellowship to work at the Department of Applied Chemistry, Kyushu University, Japan, where he explored the field of triplet-triplet annihilation-based photon up-conversion. Afterwards, he joined the 'Molecular Magnets' group at The University of Manchester, UK, where he worked on the synthesis and functionalisation of heterometallic {Cr<sub>7</sub>Ni}-based multi-qubit systems. Currently, he is an Assistant Professor in the Department of Chemistry, Ashoka University, India. His current research interests include the design and synthesis of molecular materials for optoelectronic applications.*


variety of optical applications, including low molecular weight materials for white light emission, circularly polarised luminescence, *etc.*<sup>39–49</sup> As the scope of supramolecular systems and their application is quite wide, in this review we will stay focused on the application of supramolecular interactions to create a self-assembled network of luminescent nano-architectures and its impact on the TTA-UC and CPL (Scheme 1).

## 2. Supramolecular self-assembly and photon up-conversion


Photon up-conversion is the process in which the radiated energy contains photons that are higher in energy than the incident ones. This is in contrast to the commonly observed phenomena, as during the fluorescence process some of the energy is lost in non-radiative processes and emitted light is always Stokes-shifted.<sup>50</sup> Photon up-conversion finds numerous applications in the fields of photovoltaics and photocatalysis.<sup>51,52</sup> Upconverting visible light to the ultraviolet (UV) range or near infrared (NIR) light to the visible region would increase the absorbance of any light-based devices and therefore can significantly improve their efficiency.<sup>53–55</sup> Up-conversion finds great applicability in biological processes as well. Bioimaging and photodynamic therapy (PDT) are two important areas where up-conversion could be hugely advantageous.<sup>56–61</sup> It is known that various mechanisms including nonlinear optical effects, such as the second harmonic or sum-frequency generation, the two- (or multi-) photon absorption process, *etc.*, may lead to anti-Stokes shifted emission of light.<sup>62,63</sup> Among the available photon up-conversion methods, TTA-UC represents a special case as it makes possible to upconvert low intensity light ( $\leq \text{mW cm}^{-2}$ ).<sup>35,64</sup>

In general, TTA-UC occurs through a bimolecular process in systems comprised of a donor and an acceptor chromophore. Scheme 2 represents the mechanistic profile of the TTA-UC process. The entire process could be divided in five steps: (1) absorption of incident light by a donor, (2) formation of long-lived donor triplets, (3) a donor to acceptor triplet-triplet energy transfer (TTET), (4) formation of acceptor excited singlet *via* triplet-triplet annihilation (TTA), and (5) emission of energy upconverted light.

Upon irradiation of suitable light, a donor, which is normally a heavy metal containing a porphyrin dye, gets excited to a singlet state which after passing through an intersystem crossing (ISC) step acquires a triplet state. Having an acceptor whose triplet energy level is only slightly lower than that of the donor in its proximity, a triplet energy transfer (TET) takes place. This donor to acceptor TET generates acceptor triplets, which ultimately annihilate and produce acceptor singlets.

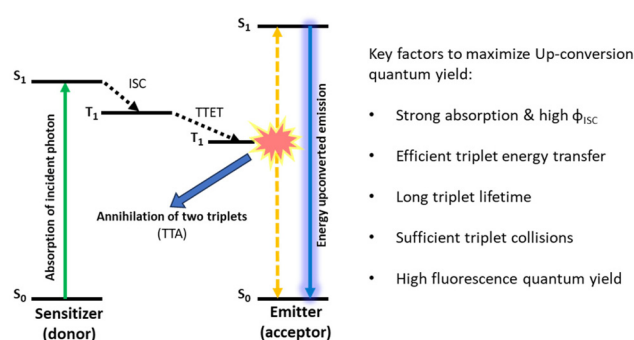

**Scheme 2** Schematic diagram depicting steps involved in TTA-UC, and the various structural features of the donor and acceptor that have a huge impact on the overall up-conversion quantum yield.

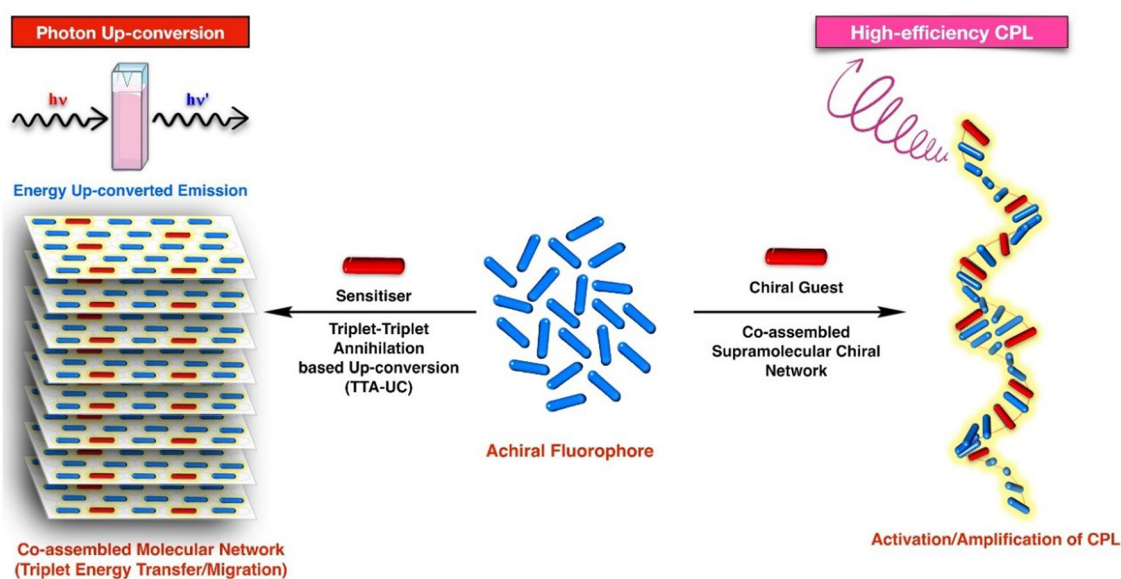

**Scheme 1** A general scheme showing various ways in which supramolecular chemistry and non-covalent interactions could be applied to fine tune the optical properties in the bulk.



The final emission takes place from this high energy excited singlet. TET (step-3) and TTA (step-4) are distance dependent events and largely responsible for the up-conversion quantum yield ( $\Phi_{UC}$ ). Another difficulty that is faced with TTA-UC is the interference from dissolved oxygen which might kill the triplets before TTA can take place. Achieving TTA-UC under ambient conditions has been a challenge.

Self-assembled networks provide an ideal platform where energy transfer processes could be controlled. A review article focusing on up-conversion in metal organic frameworks, covalent organic frameworks and gels could be found elsewhere.<sup>65</sup> In the following sections we will see how the self-assembly process can effectively circumvent both energy transfer and triplet quenching issues (*vide supra*) that limit the applicability of TTA-UC in practical life.

## 2.1 Enhancement of the TET and TTA to improve $\Phi_{UC}$

The overall quantum yield (QY) of the TTA-UC process is given by following equation:

$$\Phi_{UC} = \frac{1}{2} f \Phi_{ISC} \Phi_{TET} \Phi_{TTA} \Phi_{FI}. \quad (1)$$

As annihilation of two triplets generates one upconverted photon, a factor of  $\frac{1}{2}$  is introduced in QY calculations. Factor  $f$  represents the statistical probability of singlet formation,  $\Phi_{ISC}$  and  $\Phi_{FI}$  are the efficiencies of triplet formation in the donor and the fluorescence QY of the acceptor, respectively. The remaining two quantities in eqn (1),  $\Phi_{TET}$  and  $\Phi_{TTA}$ , depend on the intermolecular distances in the system. These two factors could be maximized to reach a value close to unity thereby increasing the  $\Phi_{UC}$ .


A TET occurs through a Dexter-type energy transfer which involves electron exchange between the two participating molecules. An intermolecular distance  $\leq 1$  nm is a prerequisite for such energy transfers. Strategies to bring donor molecules nearer to the acceptor has been thoroughly investigated. In following subsections, we will explore the three major supramolecular chemistry-based strategies that have been applied to achieve efficient photon UC. The formation of host-guest-based energy donor and acceptor supramolecular complexes, the supramolecular co-assembly of donor and acceptor mole-

cules, and the entrapment of the donor molecules in the self-assembled networks of acceptor systems have been shown to be quite successful in improving the UC efficiencies.


**2.1.1 Host-guest complex of the energy donor and acceptor chromophore.** Supramolecular host-guest complexes formed by the inclusion of a guest molecule in the macrocyclic cavity of the host system have numerous applications in biomedical fields. A wide range of host-guest complexes have been reported for drug delivery, biochemical sensing, molecular recognition, *etc.*<sup>66–69</sup> A detailed review about host-guest complexes of fluorescent dyes in aqueous media could be found elsewhere.<sup>70</sup> This supramolecular complex formation approach has also been used to achieve photon up-conversion. By improving the TET process through host-guest interactions, C. Fan *et al.* successfully demonstrated TTA-based photon UC in a perylene-boron-dipyrromethene (BODIPY) system.<sup>71</sup> The authors utilized pillar[5]arene to graft four perylenes and to be used as the host moiety (Fig. 1). A C<sub>60</sub>-BODIPY dyad functionalised to have an alkyl nitrile chain, which facilitates host-guest complex formation with a pillar[5]arene cavity, was used as a metal-free sensitizer. This cleverly designed host-guest complex of perylene-BODIPY resulted in an up-conversion system that could function at concentrations as low as  $6 \times 10^{-5}$  M with a  $\Phi_{UC}$  of up to 3.2%.

Utilizing the host-guest chemistry of cyclodextrin (CD), W. Xu *et al.* prepared 9,10-diphenylanthracene (DPA) derivatives that self-assemble in aqueous media.<sup>72</sup> Two types of derivatives were designed, one in which two  $\gamma$ -CD units are joined through a bridging DPA unit, and the second in which DPA is a tethered to  $\gamma$ -CD unit (Fig. 2). Using a Ru(II)-coumarin compound as a sensitizer and the DPA-bridged system as an emitter for TTA-UC, the authors obtained an up-conversion quantum yield in deaerated water of up to 6.87%.


Another interesting report on host-guest interaction-based up-conversion was published by Wasielewski, Stoddart and co-workers.<sup>73</sup> The group prepared a host-guest complex comprised of a fluorescent tetracationic host system (ExTzBox<sup>4+</sup>) in which a 5,15-diphenylporphyrin (DPP) sensitizer guest gets included (Fig. 3). The prepared supramolecular complex exhibited upconverted blue fluorescence when irradiated with Q bands of DPP (575 and 628 nm light). The obtained up-con-

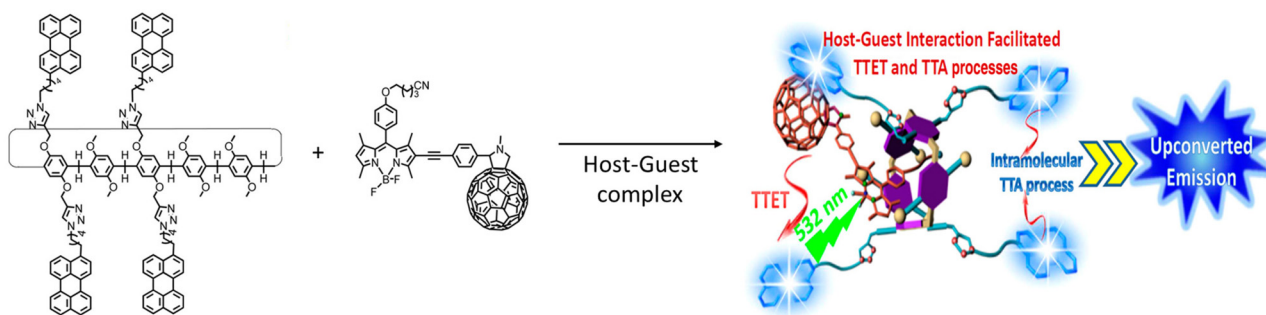

**Fig. 1** A pillar[5]arene-based host-guest complex containing perylene acceptors and a BODIPY sensitizer to exhibit TTA-UC in solution. Adopted with permission from ref. 71. Copyright 2016, American Chemical Society.

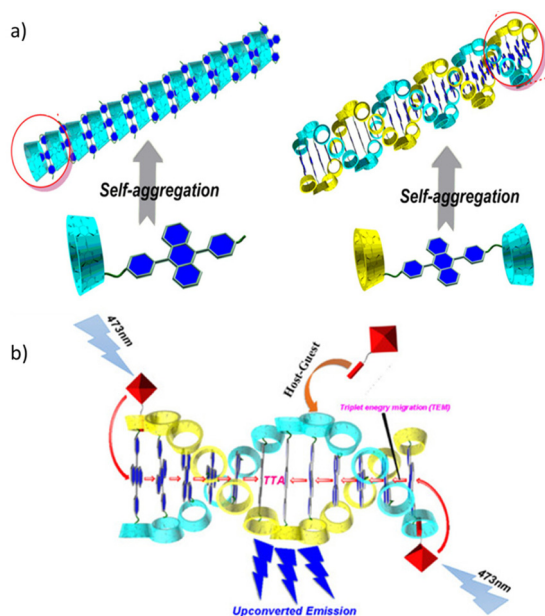

**Fig. 2** (a) Supramolecular self-assembled structure of fluorescent emitter (DPA- $\gamma$ -CD) molecules in water and (b) sensitizer guest molecules hosted in CD cavities, leading to upconverted emission through the TTA-UC mechanism. Adopted with permission from ref. 72. Copyright 2018, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

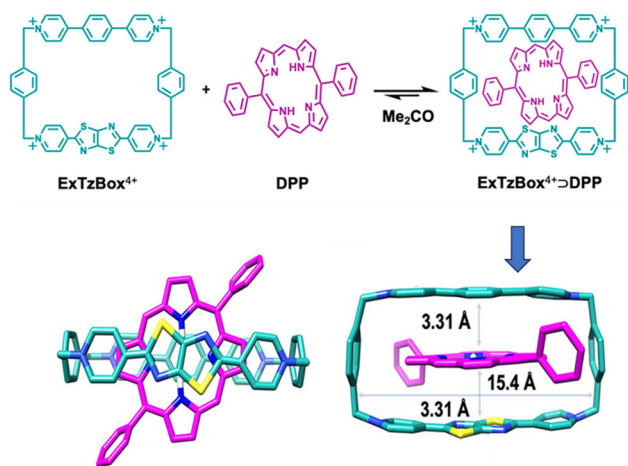

**Fig. 3** A host-guest complex for triplet fusion-based photon upconversion. Adopted with permission from ref. 73. Copyright 2020, American Chemical Society.

version quantum yields were up to 8.1% and threshold values were as low as  $4.8 \text{ mW cm}^{-2}$ . This report demonstrated the generalization of the host-guest strategy towards designing new photon up-conversion materials for specific applications.


**2.1.2 Confinement of the donor and acceptor in the supramolecular network/matrix.** One way of making sure an efficient TET from a donor/sensitizer to the acceptor molecule is to entrap the donor in a self-assembled network of acceptor units. Not only the TET, but also this approach also helps in

improving the TTA process yields as acceptors units are closely placed in a very well-organized manner. Such a system does not require diffusion, instead triplet energy migration (TEM) from one acceptor to other takes place. The involvement of TEM-based energy transfer could be confirmed by performing experiments at very low temperatures, *e.g.*, in a liquid nitrogen cooled sample. At such a low temperature, diffusion will be completely ceased and any up-conversion, if obtained, will take place only through a TEM-based mechanism.

T. Ogawa *et al.* functionalized 9,10-diphenylanthracene (DPA) to form a low molecular weight gelator (LMWG) by introducing alkyl chains that are connected *via* L-glutamate linkers (Fig. 4).<sup>34</sup> In the self-assembled structure of an acceptor and donor Pt(II)-octaethylporphyrin (PtOEP) mixture, donor molecules get dispersed and remain confined in the lipophilic regions. Phosphorescence measurements showed nearly 100% energy transfer from the donor to acceptor.

As we know that once acceptor triplets are produced, they must meet a second such acceptor molecule to allow TTA. Generally, this is achieved by diffusion in the system; however, the diffusion mechanism has some limitations as the risks of quenching are increased. In an appropriately arranged acceptor network, triplet energy can migrate without any need for molecular diffusion and therefore much improved TTA can be expected. The authors indeed reported an overall up-conversion QY of 30%. It should be noted that theoretical maximum of  $\Phi_{UC}$  is 50%. This report clearly signifies the important role of supramolecular chemistry in enhancing the energy transfer.

It is noteworthy that the commonly available acceptor chromophores are from the polyaromatic family having

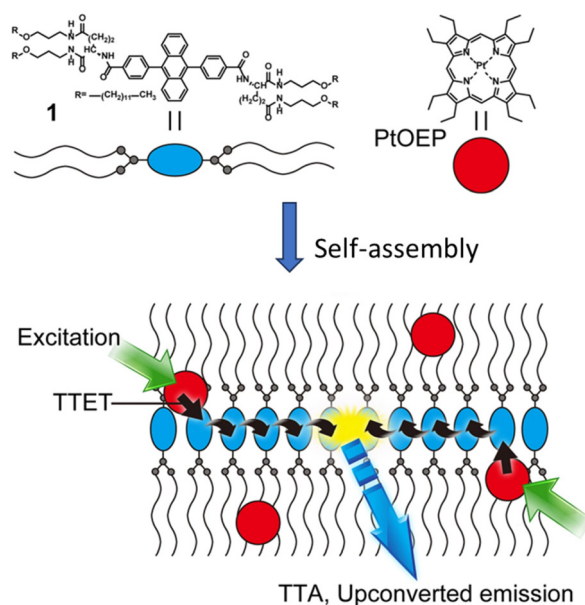


**Fig. 4** A self-assembled network of acceptor [10 mM] and entrapped donor molecules [10  $\mu\text{M}$ ], leading to extremely efficient TET and TTA processes enhancing the  $\Phi_{UC}$  up to 30%. Adopted with permission from ref. 34. Copyright 2015 Springer Nature.

minimal solubility in water. To construct a self-assembled network, these are often conjugated with long alkyl tails, which makes them further hydrophobic. D. Asthana *et al.* reported a lipid-based supramolecular system in which the acceptor arranges itself along the bilayer structure.<sup>74</sup> Lipid structures also helps in solubilizing the donor (PtOEP) which being hydrophobic in nature will have a tendency to get precipitated in water. A mixture of a cationic lipid–anionic acceptor (DPA- $\text{SO}_3^-$ ) complex and a PtOEP donor gets easily dispersed in water and exhibits TTA-UC under mild irradiation conditions ( $I_{\text{th}} = 25 \text{ mW cm}^{-2}$ ). A lipid-assisted supramolecular self-assembly resulted in an ambient condition photon up-conversion and a long triplet lifetime ( $\sim 8 \text{ ms}$ ) in aqueous media. However, the up-conversion emission intensity from the aerated sample was found to be unstable under longer irradiation times.

In a smart design adopted by R. Haruki *et al.*, a DPA-based acceptor was designed to have hydrophilic oligo(ethylene glycol) chains along with the alkyl chains to provide a self-assembled network in water medium (Fig. 5a).<sup>75</sup> Due to their hydrophobicity, PtOEP molecules remain in the alkyl tail regions. This supramolecular network displays the most desirable properties, stable TTA-UC under ambient conditions. In an aqueous medium, oligo(ethylene glycol) chains orient outwards and remain exposed to water molecules, whereas the inner part forms a very lipophilic layer.


The strategy of converting an acceptor into a gelator has certain advantages such as the formation of acceptor arrays

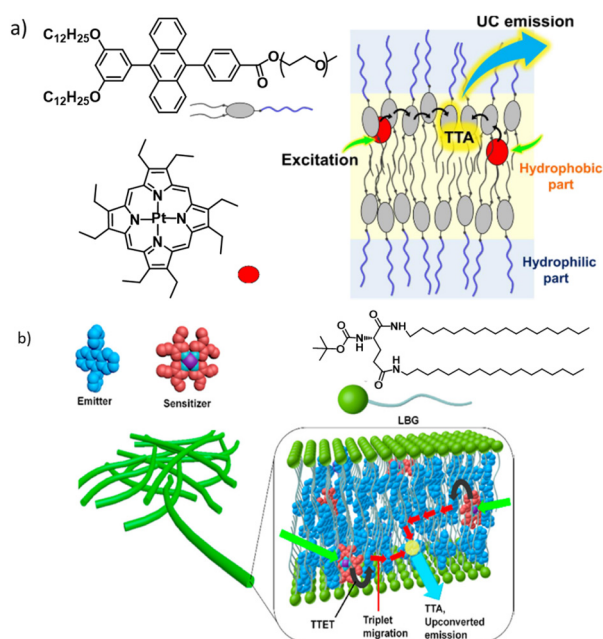

**Fig. 5** (a) A DPA-based acceptor self-assembled network showing TTA-UC in water under ambient conditions. Adopted with permission from ref. 75. Copyright 2019, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim. (b) Scheme showing the inclusion of sensitizer and acceptor chromophores in an extended fibrous network of the gel. Adopted with permission from ref. 37. Copyright 2015, American Chemical Society.

that may facilitate triplet energy migration, which can provide protection from solvent-based triplet quenching, *etc.*; however, it requires additional synthesis steps to be performed. It would be much more practical if TTA-UC could be achieved using a commonly available gelator that confines both the donor and acceptor. P. Duan *et al.* used a known gelator, *N,N'*-bis(octadecyl)-*L*-*boc*-glutamic diamide (LBG), to entrap DPA and PtOEP in their fibrous network.<sup>37</sup> A ternary mixture containing LBG, DPA and PtOEP was heated in dimethylformamide to form a clear solution. Upon cooling the entire volume forms a pink colour gel. This gel system (Fig. 5b and 6a, b) showed surprising stable photon up-conversion under air saturated conditions and exhibited a threshold ( $I_{\text{th}}$ ) value of  $1.48 \text{ mW cm}^{-2}$ , which is slightly lower than the solar irradiance. By performing a control experiment, the authors further clarified that the solvophobic interactions which force the UC chromophore pair into the nonpolar inner regions of a gel matrix are the key here. When the same LBG/PtOEP/DPA mixture was used to form a gel in a nonpolar solvent  $\text{CCl}_4$ , no UC was observed under similar conditions to the DMF gel. This difference might arise from the UC pair being dissolved and spread in the bulk  $\text{CCl}_4$  solvent environment.

The concept of applying a gelator molecule to achieve a nano-matrix assisted TTA-UC was demonstrated to be a general strategy. To be of some practical importance, it should be possible to apply with different UC pairs. The authors prepared air-saturated DMF gels of UC pairs PdPc(OBu)<sub>8</sub>/rubrene and PtTPBP/BPEA, and showed the successful UC from NIR (730 nm) to yellow (570 nm) and from red (635 nm) to cyan (507 nm), respectively (Fig. 6c and d). These experiments clearly indicated the universality of this approach.

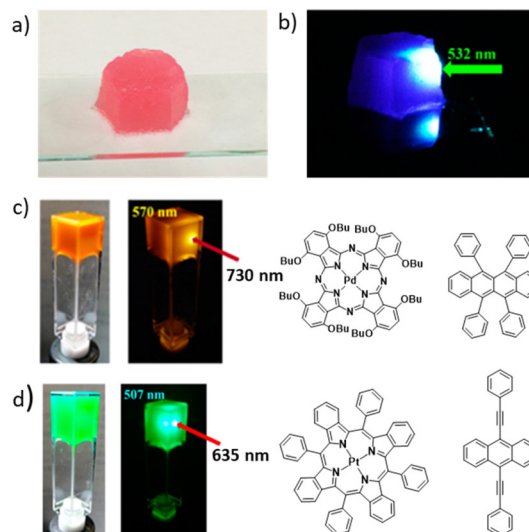

**Fig. 6** (a) DPA + PtOEP in an LBG gel matrix under normal light and (b) when irradiated with a 532 nm laser. (c and d) Generalization of the method with UC in LBG/rubrene/PdPc(OBu)<sub>8</sub> and LBG/BPEA/PtTPBP gels, respectively. Adopted with permission from ref. 37. Copyright 2015, American Chemical Society.




So far, we have discussed that how the confinement of a sensitizer in the supramolecular interactions led to the molecular assembly of acceptor chromophores or confinement of the sensitizer and acceptor chromophore in the supramolecular network of a gelator, leading to the generation of TTA-based photon up-conversion with high quantum yields and, in some cases, even in the presence of air. While the dispersion of a sensitizer (donor) in the self-assembled network of an acceptor seems extremely helpful, chances of the segregation of donor molecules remain a possibility, which might affect the overall performance of the TTA-UC system.

Co-assembly of the donor and acceptor should be able to overcome this issue. A properly functionalized donor and


acceptor might form a supramolecular network in which both units are included homogeneously. P. Duan *et al.* reported a TTA-UC system comprised of a cyano-substituted distyrylbenzene acceptor and Pd(ii) mesoporphyrin IX donor systems (Fig. 7).<sup>76</sup> The acceptor alone showed an aggregation induced enhancement in fluorescence intensity. Interestingly, this co-assembled network exhibited temperature-dependent turn on/off UC. When heated to form a solution, the UC was lost, whereas upon cooling back to the gel state, UC was regained.

Confinement of the donor or acceptor in host cavities require a size match with the guest structure. This might be a restrictive condition in generalising the host-guest interaction-based upconverting materials. Q. Guo *et al.* suggested the applications of a dendritic network of acceptor units and the utilization of various spaces in the three-dimensional dendrimer network to accommodate sensitizer molecules.<sup>77</sup> An investigation in methanol and a methanol/water mixture revealed a huge difference in up-conversion yields. It was found that addition of water triggered the formation of self-assembled nanoparticles ranging up to 250 nm in size. Sensitizer molecules get confined in those cavities increase the  $\Phi_{UC}$  from 1.4% in methanol to 10.2% in the methanol/water medium.

**2.1.3 Self-assembly led to ambient condition TTA-UC in water.** TTA-UC is an attractive technique to upconvert low frequency radiation into a higher one as it requires much milder conditions to operate. In fact, it has been shown to work with incident light intensities that fall under solar light irradiance, which increases its applicability in real life devices to several folds.<sup>37,78–84</sup> However, as this technique relies on the formation and lifetime of triplets, it is quite sensitive to quenching by the dissolved oxygen. Therefore, in most cases the experiment must be performed in completely degassed or de-aerated solvents, making it difficult to realize in water. P. Bharmoria *et al.* devised a co-assembly-based method in which gelatin, a surfactant, and chromophores are mixed to form a hydrogel, and reported an air-stable up-conversion with a  $\Phi_{UC}$  of 13.5%.<sup>85</sup> The donor PtOEP and the acceptor DPA-SO<sub>3</sub>Na get accumulated in the lipophilic regions of the surfactant which lies under a thick cover made of a hydrogen-bonded gelatin network (Fig. 8). Oxygen blocking in such a biopolymer-surfactant-chromophore co-assembly represented an exciting way of producing upconverted light.

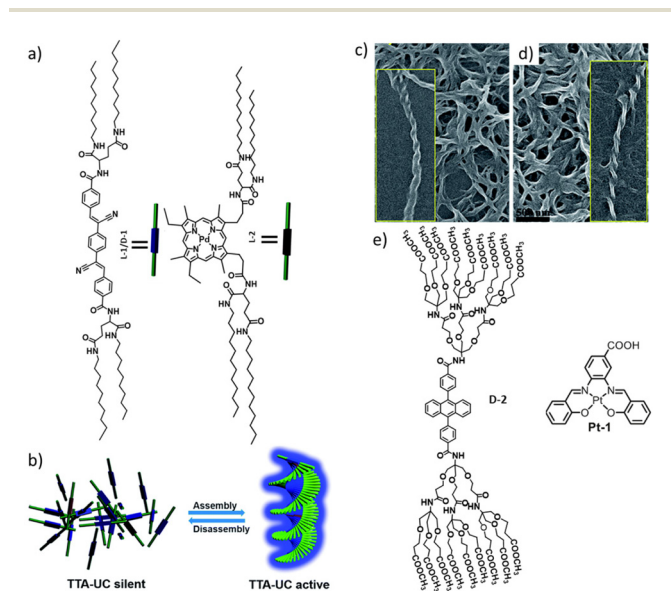


**Fig. 7** (a and b) Co-assembly of functionalized donor and acceptor units, leading to an aggregation-induced enhancement of fluorescence. Influence of the chiral glutamic acid linker is seen from the TEM image that showed the formation of helical nano structures in both acceptor (c) and donor gel samples (d). Adopted with permission from ref. 76. Copyright 2017, RSC. (e) Chemical structures of the DPA-based dendritic acceptor molecule and the Schiff-base-based Pt-acceptor system. Adopted with permission from ref. 77. Copyright 2020, Elsevier Ltd.

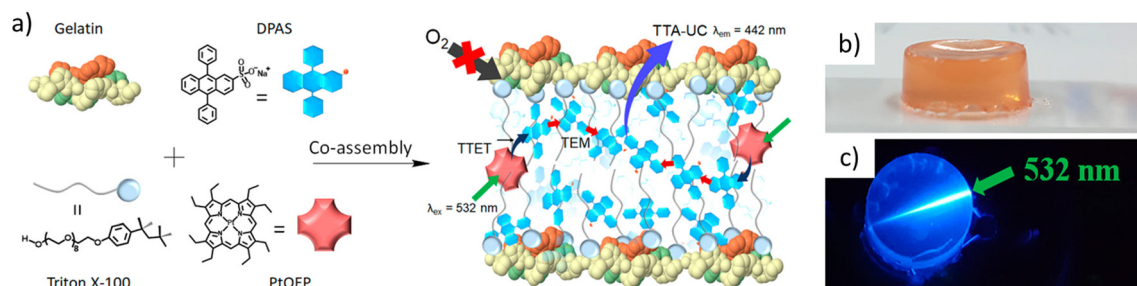

**Fig. 8** (a) Scheme showing the formation of a UC pair-surfactant-gelatin co-assembly in water and (b and c) a co-assembled hydrogel in normal light and upon irradiation with a 5432 nm laser. Adopted with permission from ref. 85. Copyright 2018, American Chemical Society.

In a slightly different approach, H. Kouno *et al.* modified the DPA acceptor to have ten carbon long alkyl chains and quaternary ammonium groups on both sides, giving it an amphiphilic characteristic.<sup>32</sup> A tetracarboxylic acid analogue of PtOEP was synthesized to overcome the insolubility issue. A modified donor and acceptor when dissolved in water leads to the formation of a co-assembled network. Up-conversion measurements performed in aerated water showed stable UC signals. Furthermore, extending the co-assembly approach to a slightly different type of supramolecular network, H. Kouno *et al.* investigated the effect of supramolecular crowding by introducing a fatty acid anion in the system.<sup>86</sup> DPA functionalized with four quaternary ammonium groups present at the end part of an alkyl tail was prepared (Fig. 9a). As expected, the functionalized acceptor forms a self-assembled network in water, this supramolecular assembly failed to exhibit UC in aerated water (Fig. 9b). Sodium oleate was then introduced into the acceptor and PtOEP mixture, and a co-assembled network was developed in water. Addition of sodium oleate reduces the electrostatic repulsion between the ammonium groups and results in a much tighter supramolecular network formation, which is now capable of blocking the oxygen. This

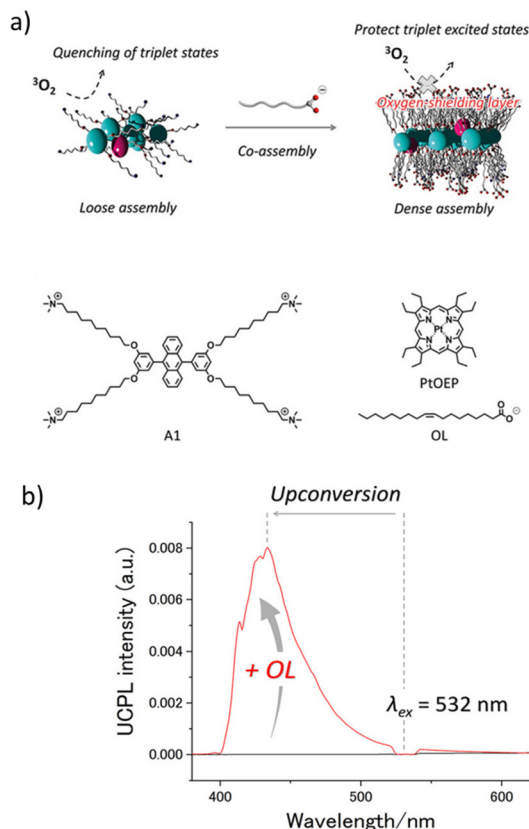


**Fig. 9** (a) Chemical structure of the functionalized DPA acceptor and scheme showing a co-assembled network that blocks the oxygen. (b) Plots showing the successful UC emission from the oleate–acceptor–PtOEP assembly and no UC from acceptor–PtOEP assembly in water. Adopted with permission from ref. 86. Copyright 2019, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

co-assembled network exhibited a remarkably high up-conversion quantum yield in deaerated water of 19.8%. Up-conversion measurement performed in an air saturated water medium gave a  $\Phi_{\text{UC}}$  of up to 14.4%.

Y. Kawashima *et al.* prepared a bola-type amphiphile acceptor and mixed it with decanoate.<sup>87</sup> A sensitizer mixed with an acceptor and decanoate forms a co-assembled network in water. Upon excitation with 445 nm light, an upconverted emission at 390 nm was observed. In order to calculate the oxygen barrier efficiency of this ternary mixture, the UC efficiencies of aerated and deaerated samples were compared and they were found to be nearly 80%.

It is evident that the energy transfer processes are most efficient when there is a well organised molecular network of the participating chromophores. In this context, metal organic frameworks (MOFs) present a very suitable platform. J. Park *et al.* synthesized a water stable Zr-MOF of 4,4'-(9,10-anthracenediyl)dibenzoic acid (DCDPA) and demonstrated the successful TTA-UC using a Pd(II)-meso-tetrakis(4-carboxyphenyl)porphyrin (Pd-TCPP) sensitizer (Fig. 10).<sup>88</sup> During the MOF synthesis, varying amounts of a sensitizer were taken with different concentration ratios of the sensitizer and annihilator. Sensitizer molecules get included in the defect coordination sites of Zr clusters. Transmission electron microscopy images revealed the formation of an octahedral structure of around 55 nm. Up-conversion measurement in an aqueous medium showed an up-conversion efficiency of 1.28% under illumination of  $2.4 \text{ mW cm}^{-2}$  intensity light. The prepared MOF was found to be photostable when irradiated with a laser power intensity of up to  $100 \text{ mW cm}^{-2}$ , and also no cytotoxicity in HeLa cells was observed.

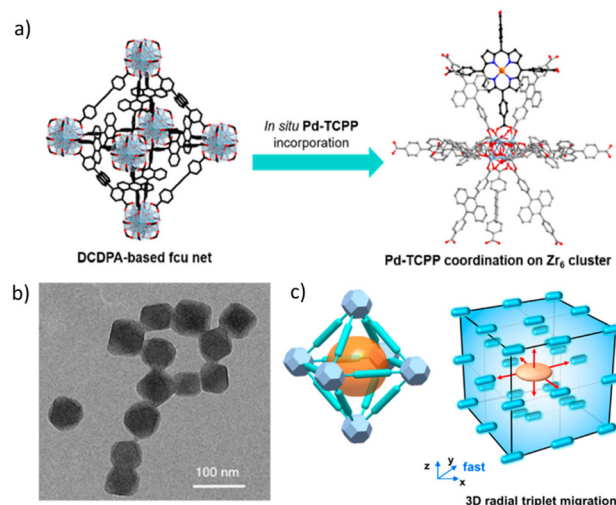

**Fig. 10** (a) Schematic diagram showing the preparation of a MOF containing an annihilator DCDPA and a sensitizer Pd-TCPP. (b) TEM image showing octahedral MOF structures. (c) Schematic design showing the three-dimensional triplet energy migration paths of the MOF. Adopted with permission from ref. 88. Copyright 2018, American Chemical Society.



Photon up-conversion under ambient conditions and in aqueous media broadens the overall applicability of these systems in biological processes such as bio-imaging and PDT.

### 3. Supramolecular self-/co-assembly and CPL

Word light refers to the visible part of electromagnetic (EM) radiation, which is a tiny part of the spectrum that extends from very short wavelength  $\gamma$ -rays to long wavelength radio waves. Human eyes are sensitive to only the visible part of it and cannot detect the remaining electromagnetic radiation. EM radiation contains two components, electric and magnetic fields, which oscillates in a mutually perpendicular direction along the wave propagation axis. Unpolarized light has electric field vectors oscillating in all possible planes perpendicular to the wave propagation direction. Light is said to be polarized if by passing the light through a polarizer, the random oscillations are filtered out.<sup>89,90</sup> Depending on the electric field orientation in the polarized light, it could be categorised into three types: linearly polarized, circularly polarized, and elliptically polarized light.

Curiosity about the polarized light started with the initial studies carried out by Christiaan Huygens and Erasmus Bartholinus (1669). In 1809, E. L. Malus explained the phenomenon of double refraction from the crystals of spar producing double images using the word “polarization”. During 1811–1817, a French physicist Jean Baptiste Biot discovered the rotation of the plane of polarization upon passing the polarized light through a properly cut quartz. Materials capable of rotating the plane of polarized light are called optically active. Optical activity is displayed by chiral systems.

Chirality is the property of a system which illustrates that the structure and its mirror image are non-superimposable. Chiral objects are found ubiquitously in nature and in many cases are endowed with characteristic chiroptical properties.<sup>91</sup> There are several chiroptical methods that are used to characterize the stereochemical and electronic properties of chiral molecules. Standard measurements performed to investigate chiroptical properties are circular dichroism (CD) and optical rotatory dispersion. Being an absorption-based method, the CD spectrum contains information about the ground state chiroptical properties of any chiral system. CD spectroscopy is based on the differential absorption of left- and right circularly polarised light, and has become a widely used technique.<sup>89,92–95</sup> Circularly polarized luminescence (CPL) is the phenomenon that produces polarized emission light (Scheme 3). CPL measurements hold information about the excited electronic states of chiral systems. Like CD spectroscopy, CPL measures the difference in left- and right-circularly polarised emissions from the system.<sup>96–98</sup> With the introduction of commercially available spectrometers for CPL measurements, the field of CPL has seen a huge surge in research activity. This has resulted in a large number of publications reporting CPL-active systems, a themed collection on



**Scheme 3** Diagram showing the procedure to obtain circularly polarized light using a physical method and the emission of circularly polarized light from a chiral CPL-active fluorophore.

this topic recently published in *Journal of Materials Chemistry C* (Royal Society of Chemistry, 2023) is an example of that.

CPL materials find varied applications in different domains namely chiral opto-electronics, biological fields like chemosensors, light emitting transistors, CPL switches, 3D-displays, etc.<sup>99–109</sup> CPL has also been applied to amplify the chirality in molecular/supramolecular systems.<sup>110–115</sup> One of the criteria used to describe CPL-active systems is the luminescence dissymmetry factor ( $g_{lum}$ ) which may lie between +2 and –2, positive indicating left-handed circularly polarised light and negative indicating right-handed circularly polarised light.

$$g_{lum} = 2(I_L - I_R)/(I_L + I_R) \quad (2)$$

Organic molecules usually exhibit smaller  $g_{lum}$  compared to inorganic compounds. However, as organic molecules could be easily modified to meet specific requirements, they represent vast opportunities of creating efficient and more benign CPL-active materials.<sup>116,117</sup> Various strategies have been opted to produce new CPL-active molecules and/or to amplify the CPL signal of existing materials.<sup>118–121</sup>

A supramolecular chemistry-based approach has been particularly helpful at this. In the coming section, we will discuss some of the representative examples where supramolecular engineering has resulted in induced CPL activity or caused amplification in polarized luminescence and  $g_{lum}$  values.

#### 3.1 CPL from supramolecular assemblies of the achiral chromophore: chirality transfer vs. chiral energy transfer (C-FRET)

Induction or amplification of chirality is the process in which doping an achiral system with a small amount of a chiral analogue creates chiral assemblies in the bulk. This is known as the “majority rule” or “sergeants and soldiers” principle.<sup>122–128</sup> This approach has been widely applied in the field of helical polymers, supramolecular polymers, etc.<sup>127,129–135</sup> In the context of CPL, induction of chirality through the majority rule

could be extremely helpful as the preparation of chiral luminescent systems would not be a requirement. Simple doping with a small amount of a chiral analogue would make the entire system CPL active.

In some cases, chirality could be acquired upon supramolecular self/co-assembly formation.<sup>136,137</sup> Such systems allow the use of an achiral chromophore for chiroptical applications. P. Duan, M. Liu and co-workers prepared benzene-1,3,5-tricarboxamide benzoic acid (BTABA), a symmetric molecule that forms a gel in a DMF/H<sub>2</sub>O mixture.<sup>138</sup> When this gel is heated to form a solution and then vortexed, chiral assemblies are formed which are then used as a chiral seed (Fig. 11). A fluorescent dye was then added to this chiral assembly. CPL measurement using this dye doped chiral assembly exhibited a  $g_{lum}$  value of  $\pm 0.0435$  (at 465 nm).

The authors further extended this approach to accommodate photon upconverting materials inside the chiral assemblies obtained from BTABA to realize CPL from upconverted emission.<sup>139</sup> A 9,10-diphenylanthracene derivative as a TTA-UC acceptor and a Pt(II) mesoporphyrin IX (PtMIX) donor were mixed with BTABA to form a co-assembled network. When irradiated with 532 nm light, an upconverted emission at 434 nm was observed. CD measurements confirmed the supramolecular chirality transfer from the BTABA gel to the acceptor chromophore. Upon excitation with a 532 nm laser, CPL activity from the upconverted emission (at 445 nm) with a  $g_{lum}$  value of  $\pm 0.014$  was successfully recorded.


DNA is a naturally occurring chiral system and has been used to attach fluorophore units to achieve CPL. A synthetically less demanding route could be to use DNA nanostructures as a template to incorporate fluorescent dyes for CPL. Q. Jiang *et al.* applied a carbazole-based bicyanin dye to obtain a DNA-cyanine composite.<sup>140</sup> When bound to DNA, the dye gets confined in a restricted environment and therefore the fluorescence intensity gets increased by a noticeable amount. Their study showed that a decrease of GC contents in a duplex DNA-biscyanine assembly resulted in an increase of fluo-

rescence intensity and CPL emission. This observation was attributed to the preferential binding of the biscyanine dye to AT-rich dsDNA. Also, longer DNA duplex templates exhibited stronger CD signals and CPL activities. B.-C. Kim *et al.* demonstrated CPL activity in a liquid crystalline mesophase obtained from the assembly of achiral molecules.<sup>141</sup> The authors employed a 1:1 mixture of a rod-shaped molecule (blended with a small amount of pyrromethene dye) and a bent-core host system. In the mixed state, dye molecules follow a mesogen ordering pattern. Utilization of the chiral spaces in the liquid crystalline host eliminates the need for multi-step chemical functionalization of the fluorophore to introduce a chiral centre in it.


Host-guest chemistry has also been proven to be an important tool to realize CPL from an achiral fluorophore. T. Li *et al.* used a sulfonate group containing naphthalene-based dye that binds with a chiral macrocycle (Fig. 12) through hydrogen bonding.<sup>142</sup> This molecular host-guest complex exhibited induced CD and CPL. However, the observed dissymmetry factor was rather low (0.0005).

K. Q. Le *et al.* reported CPL from an achiral dye displaying strong dissymmetry between left- and right polarised light ( $g_{lum} > 0.1$ ) using chiral metal nanoarchitectures.<sup>143</sup> The authors demonstrated when achiral dye molecules were placed close to the chiral nanoparticles, through near-field interactions with chiral plasmons, an enhancement in photoluminescence takes place. For their study, the group fabricated a 50 nm thick two-dimensional chiral nanostructure of Au on a glass substrate using the electron beam lithography technique. A thin film of IR125 dye/polyvinyl alcohol (1:1) was deposited over the chiral nanostructures.


It appears that in systems in which one component is chiral and the other is achiral, chirality induction is essential to exhibit CPL. An interesting study performed by K. Yang *et al.* ruled this out by demonstrating the energy transfer of circularly polarized light to an achiral acceptor that finally emits circularly polarized light.<sup>144</sup> The authors designed two modes of investigations to show that chirality transfer between the donor and acceptor dyes is not required. A CPL-active helical polyacetylene copolymer containing pyrene units was employed as an energy donor. Films of only the donor, only the acceptor and a blend film containing a mixture of the donor and acceptor were prepared by using a poly(vinyl butyral) polymer matrix (Fig. 13a and c). By putting individual

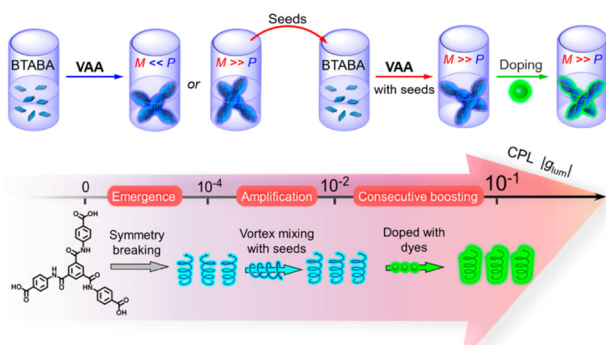

**Fig. 11** Scheme showing chiral aggregate formation from an achiral molecular system and then utilizing it as a chiral seed for further chiral supramolecular network formation (top). The scheme below shows the emergence of supramolecular chirality, leading to a CPL signal when doped with a fluorescent dye. Adopted with permission from ref. 138. Copyright 2020, American Chemical Society.

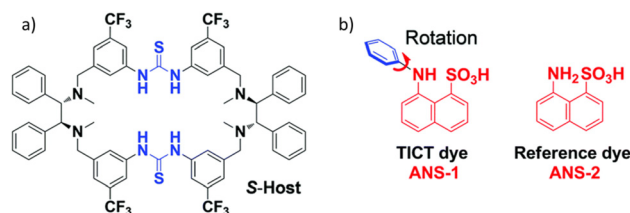

**Fig. 12** Chemical structures of the chiral host (a), and the achiral fluorescent guest (b). Adopted with permission from ref. 142. Copyright 20210, Royal Society of Chemistry.

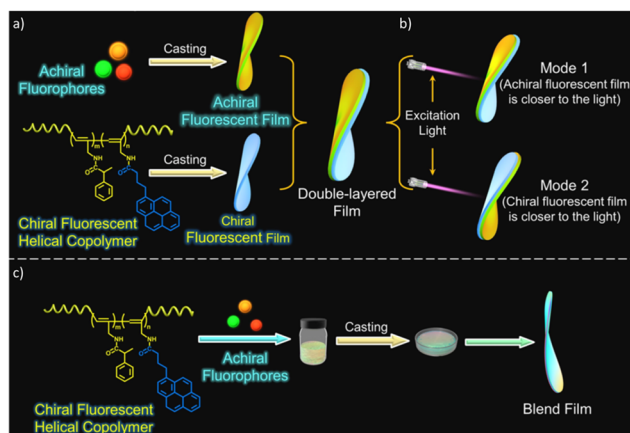

**Fig. 13** Schematic diagrams showing the formation of double layer film (a), two different modes of investigation with double layer film (b), and formation of blend films (c). Adopted with permission from ref. 144. Copyright 2023, American Chemical Society.

chiral/achiral fluorophore films together in a side-by-side fashion, double layer films were prepared. Double layer films were investigated in two modes, once putting an achiral film side nearer to the excitation source and then reversing the film to put a chiral fluorophore film closer to the excitation light source (Fig. 13b). When subjected to CPL measurements, both types of films, the double layer and the blend layers showed CPL signals corresponding to the emission of an achiral fluorophore through energy transfer processes. An interesting phenomenon was observed when observation modes for the double layer sample was changed. Changing the mode resulted in a change from the left- to right-handed CPL output and *vice versa*.


Another very recent work from Z.-W. Luo *et al.* demonstrated a nonradiative chiral energy transfer from the chiral donor to achiral energy acceptor fluorophore exhibiting bright CPL.<sup>145</sup> The authors synthesized a tri-cholesteryl-based emis-

sive polymer, poly(4,4',4''-tricholesterylformate-oxytetraphenyl-ethylene-methyl) acrylic acid ester, that exhibited a quantum yield of 21% in the solid state (Fig. 14a). Successful CPL with a  $g_{lum}$  value of +0.18 was observed when the polymer content in the plasticizer was above 20%. When Nile red dye (an achiral acceptor fluorophore) was mixed with a CPL-active polymer-plasticizer mixture, excitation at 360 nm resulted in narrower emission bands from the polymer unit with a concomitant increase in the emission band corresponding to Nile red (NR) dye, indicating an FRET-based energy transfer from the donor to acceptor.

CPL measurements revealed the appearance of a new CPL peak at around 600 nm corresponding to NR (Fig. 14b). A composition containing 1% NR when excited with 360 nm light initiates an energy transfer from the donor to acceptor, causing circularly polarized emission at 625 nm with a  $g_{lum}$  value of +0.20. The same mixture when was excited at 470 nm, a weak CPL signal was observed. This implies that NR dyes acquired some chirality through induction from the chiral polymer present in the mixture; however, the  $g_{lum}$  value was about five-time smaller.

A recent report, published by Y. Bao *et al.*, represents a beautiful example of co-assembly-based tuning of the CPL wavelength and  $g_{lum}$  value in a ternary mixture, comprised of two achiral fluorophores and a nonfluorescent chiral component.<sup>146</sup> A mixture of poly(9,9-di-*n*-octylfluorene), coumarin-6 and *R/S*-limonene displayed a chiral energy transfer (C-FRET)-based CPL with improved  $g_{lum}$  value (Fig. 14c). A co-assembly-supported FRET led to a green colour CPL from the originally blue CPL light.

The chiral energy transfer between donor-acceptor fluorophore could be maximized in a system in which electric and magnetic transition dipoles are coupled. J. Wade *et al.* investigated the impact of such dipolar coupling on the overall CPL by preparing an FRET system comprised of a chiral superhelicene (acceptor) and an achiral polymer matrix (energy donor). CD measurement revealed the formation of a chiral phase that

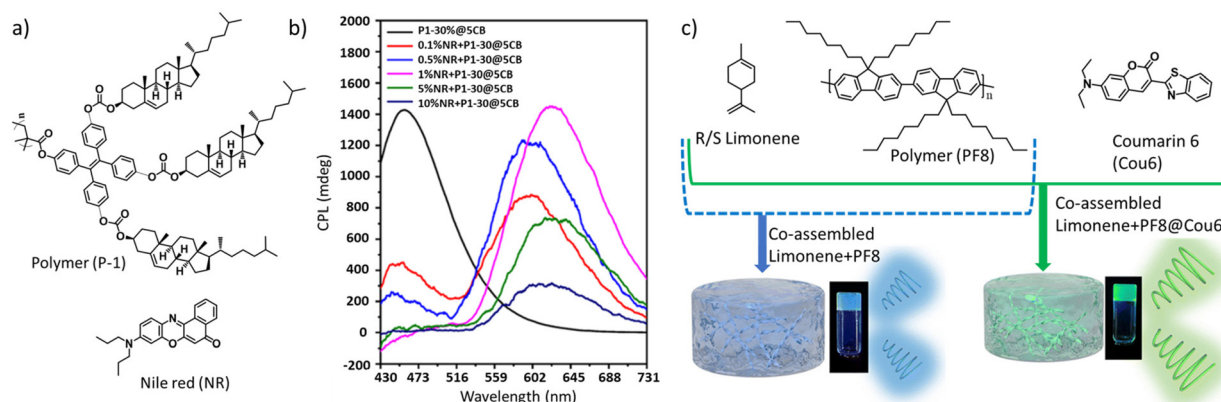

**Fig. 14** (a) Chemical structures of the emissive polymer (P-1) and achiral dye (Nile red). (b) CPL activity from mixtures containing varying amounts of the NR dye and 30% polymer mixed in a plasticizer (5CB). Adopted with permission from ref. 145. Copyright 2023, American Chemical Society. (c) C-FRET from a co-assembled ternary mixture of an achiral dye polymer (PF8), coumarin 6 (Cou6) and *R*- (or *S*)-limonene, leading to enhanced  $g_{lum}$ . Adopted with permission from ref. 146. Copyright 2023, Royal Society of Chemistry.



displayed an approximately six-time stronger chiroptical signal than the helicine alone. Their study found an unprecedented enhancement in CPL ( $\sim 500$ -fold amplification).<sup>147</sup>

### 3.2 Self-assembly/crystallization-driven amplification of CPL


With the increasing interest towards the fabrication of optical devices based on CPL, various strategies have been explored to make achiral systems CPL active (*vide supra*). A straightforward way is to perform synthetic modification to convert an achiral chromophore into a chiral one. Another approach, rather a simple and less challenging way of obtaining CPL is chirality transfer, which has been proven to be an effective method to generate circularly polarized light. Chirality sometimes could also be achieved through a self-assembly process in which hierarchical helical architectures are formed.<sup>136,148–163</sup>

Attainment of chirality in an achiral molecular network through supramolecular interactions has been called a “soft approach” of generating chiral structures.<sup>150</sup> The main driving force behind the chiral organization in the bulk could be twisting of ligands or metals with specific binding positions. S.-Y. Yu *et al.* prepared a luminescent chiral supramolecular Au ring that self-assembled from Au<sub>2</sub> monomers.<sup>164</sup>

Chiroptical properties are directly correlated to crystal space groups. Though it is not very common to observe and difficult to predict, it is possible to crystallize achiral molecules into chiral space groups. This has been well described by L. Caswell *et al.* as “optical activity can be created from nothing”.<sup>165</sup> J. Zhao *et al.* demonstrated the CPL from an achiral organic–inorganic hybrid complex of manganese.<sup>166</sup> The authors employed potassium(dibenzo-18-crown-6) as a cation to form [K(dibenzo-18-crown-6)]<sub>2</sub>MnX<sub>4</sub> cocrystals where X is a halide. Single crystal X-ray diffraction studies revealed a non-centrosymmetric space group, monoclinic *Cc*. Microarea optical activity tests showed a successful exhibition of CPL from the single crystals and in some cases from the powder sample as well.

Taking advantage of the Pfeiffer effect,<sup>167</sup> G. Park *et al.* demonstrated an amplified circularly polarized phosphorescence in a square planar Pt(II) complex.<sup>168</sup> In the co-assembled structure containing a small fraction of the chiral version of the Pt complex (Fig. 15a), they observed a two orders of magnitude increase in the  $g_{lum}$  value with respect to the chiral complex alone.

It is noteworthy that the achiral Pt complex referred to as a soldier, forming a helical self-assembled network even in the absence of the chiral Pt complex (sergeant). Helical stacking is driven by the presence of nonyl chains. However, no CPL activity could be observed from the self-assembled network, probably due to the presence of equal amounts of right- and left-handed stacked structures. Addition of a small amount of the chiral Pt complex (sergeant) resulted in an increase of the enantiomeric excess of the one type of helicity in the self-assembled structures. In co-assembled structures, a metal–metal interaction (MMLCT) was observed in the form of a weak absorption band at around 500 nm (Fig. 15b). The electronic CD spectra (ECD) showed the formation of a P- or

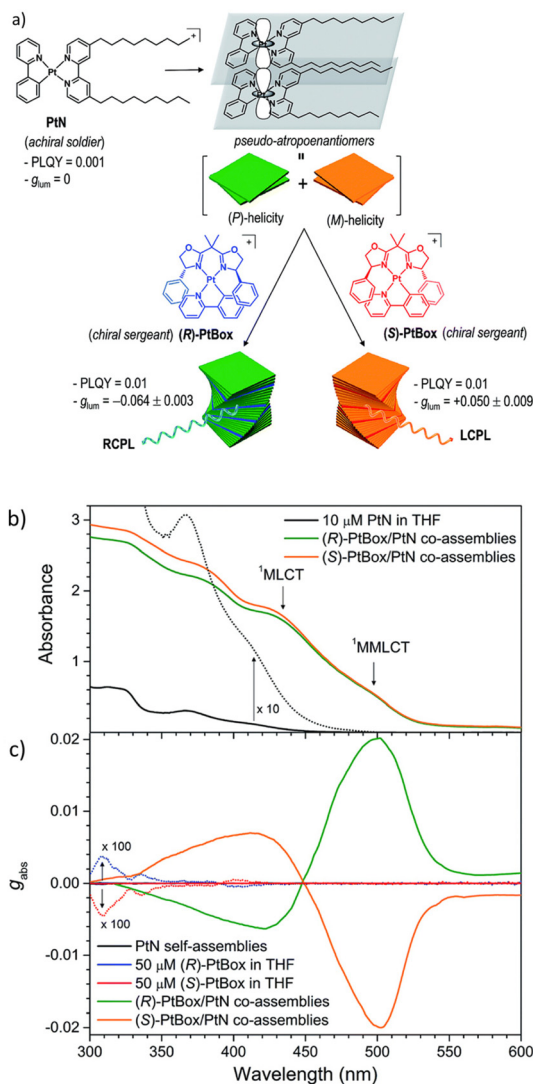

**Fig. 15** (a) Schematic diagram showing the co-assembled structure of chiral and achiral Pt complexes. (b) and (c) Absorption spectra and the ECD spectra, respectively. Adopted with permission from ref. 168. Copyright 2018, Royal Society of Chemistry.

M-type helical supramolecular network depending on the chirality of the added sergeant (Fig. 15c). This work represents an ideal example of applying supramolecular self-assembly tactics to generate and modulate symmetry-controlled properties such as CPL.

## 4. Conclusions

Supramolecular chemistry is governed by the weak noncovalent reversible intermolecular forces. When in action, these distance and direction dependent interactions, such as intermolecular hydrogen bonds, dictate the molecular arrangement in the assembled structures. Chemical engineering of the building block/supramolecular synthon has led to the formation of some extraordinarily large molecular structures with

excellent precisions. For example, utilization of the interaction between the pyridyl ligand and metal ions such as Pd(II) or Pt(II) has resulted in the generation of some very interesting molecular boxes/cages.<sup>169–171</sup> This approach has resulted in the development of a vast number of supramolecular assemblies that find diverse applications in a broad range of fields including encapsulation, drug delivery, molecular recognition, ion transport, artificial photosynthesis, photocatalysis, self-healing systems, investigation of photo-reactions in confined spaces, *etc.*<sup>170,172–175</sup> Recently, the self-assembly of peptides and proteins and DNA nanotechnology have attracted huge attention as they allow the formation of highly ordered nanostructures with nearly absolute control over the shape and geometry.<sup>2,176–179</sup> DNA origami-based nanotechnology has been predicted to have potential impact in various research fields, especially in biomedical applications.<sup>180–182</sup>

The might of the supramolecular-self-assembly approach, a simple yet extremely powerful method, has already been proven in the fields of biology and soft materials. Herein, we have reviewed its huge potential in designing materials for emerging applications such as photon up-conversion and circularly polarized luminescence. Molecular self-/co-assembly (*vide supra*) has direct influence on the following inter-molecular processes that play crucial roles in TTA-UC:

1. Triplet-triplet energy transfer is enhanced in a properly positioned donor-acceptor network.
2. The formed acceptor triplets have greater chances of annihilation (TTA) in such closely placed acceptor arrays.
3. Triplet energy migration becomes a dominant energy transfer route making the entire process more efficient.
4. The self-assembled network may provide a shield from the quenchers present in the solvent/environment.
5. The supramolecular assembly may help in achieving a much longer triplet lifetime.

In the case of CPL, the supramolecular self-/co-assembly may be applied in the following three ways to generate or amplify the CPL response:

1. An achiral fluorophore co-assembled with a non-luminescent chiral matrix.
2. An achiral fluorophore self-assembled to form a chiral supramolecular network.
3. A chiral fluorophore self-assembled network.

In other words, application of the supramolecular strategy may allow even an achiral fluorophore to exhibit CPL. A co-assembled network of a judiciously chosen fluorophore pair may lead to energy down-converted CPL (*via* FRET). As supramolecular interactions are sensitive to external stimuli such as pH, temperature, mechanical disturbances, *etc.*, stimulus responsive CPL can also be designed. Additionally, CPL in an energy up-converted (TTA-UC) system could also be achieved.

To conclude, this strategy holds tremendous potential towards designing future photon up-conversion and circularly polarized luminescent materials. Photon up-conversion materials that may work under illumination of sunlight would have an immense impact on the current solar energy-based techniques.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

AS, GR and ARL are thankful to Ashoka University for their doctoral research fellowship. DA is thankful to the Axis Bank Grant for funding the photon up-conversion project.

## References

- 1 J.-M. Lehn, *Angew. Chem., Int. Ed. Engl.*, 1988, **27**, 89–112.
- 2 Q. Luo, C. Hou, Y. Bai, R. Wang and J. Liu, *Chem. Rev.*, 2016, **116**, 13571–13632.
- 3 J. W. Steed and J. L. Atwood, *Supramolecular chemistry*, Wiley-Blackwell, John Wiley & Sons, Inc., Hoboken, 3rd edn, 2021.
- 4 J.-H. Deng, J. Luo, Y.-L. Mao, S. Lai, Y.-N. Gong, D.-C. Zhong and T.-B. Lu, *Sci. Adv.*, 2020, **6**, eaax9976.
- 5 P. Li, M. R. Ryder and J. F. Stoddart, *Acc. Mater. Res.*, 2020, **1**, 77–87.
- 6 L. Zhang, X. Zhong, E. Pavlica, S. Li, A. Klekachev, G. Bratina, T. W. Ebbesen, E. Orgiu and P. Samori, *Nat. Nanotechnol.*, 2016, **11**, 900–906.
- 7 V. Allain, C. Bourgaux and P. Couvreur, *Nucleic Acids Res.*, 2011, **40**, 1891–1903.
- 8 D. M. Bassani, L. Jonusauskaite, A. Lavie-Cambot, N. D. McClenaghan, J.-L. Pozzo, D. Ray and G. Vives, *Coord. Chem. Rev.*, 2010, **254**, 2429–2445.
- 9 S. Mohnani and D. Bonifazi, *Coord. Chem. Rev.*, 2010, **254**, 2342–2362.
- 10 A. R. Hirst, B. Escuder, J. F. Miravet and D. K. Smith, *Angew. Chem., Int. Ed.*, 2008, **47**, 8002–8018.
- 11 A. J. Savyasachi, O. Kotova, S. Shanmugaraju, S. J. Bradberry, G. M. Ó'Máille and T. Gunnlaugsson, *Chem*, 2017, **3**, 764–811.
- 12 T. Keijer, T. Bouwens, J. Hessels and J. N. H. Reek, *Chem. Sci.*, 2020, **12**, 50–70.
- 13 X. Ma and Y. Zhao, *Chem. Rev.*, 2015, **115**, 7794–7839.
- 14 Q. Zhang, D.-H. Qu, H. Tian and B. L. Feringa, *Matter*, 2020, **3**, 355–370.
- 15 A. Ciesielski and P. Samori, *Nanoscale*, 2011, **3**, 1397.
- 16 I. V. Kolesnichenko and E. V. Anslyn, *Chem. Soc. Rev.*, 2017, **46**, 2385–2390.
- 17 A. P. Silva, H. NimaláGunaratne, P. MarkáLynch, E. Glenn and K. SamankumaraáSandanyake, *Chem. Soc. Rev.*, 1992, **21**, 187–195.
- 18 F. J. Hoeben, P. Jonkheijm, E. Meijer and A. P. Schenning, *Chem. Rev.*, 2005, **105**, 1491–1546.
- 19 X. Cao, A. Gao, J.-T. Hou and T. Yi, *Coord. Chem. Rev.*, 2021, **434**, 213792.
- 20 X. Dou, N. Mehwish, C. Zhao, J. Liu, C. Xing and C. Feng, *Acc. Chem. Res.*, 2020, **53**, 852–862.

- 21 E. Busseron, Y. Ruff, E. Moulin and N. Giuseppone, *Nanoscale*, 2013, **5**, 7098–7140.
- 22 S. I. Stupp and L. C. Palmer, *Chem. Mater.*, 2014, **26**, 507–518.
- 23 D. B. Amabilino and P. A. Gale, *Chem. Soc. Rev.*, 2017, **46**, 2376–2377.
- 24 C. Mongin, C.-K. Liang, B. Bibal and D. M. Bassani, *Pure Appl. Chem.*, 2017, **89**, 269–277.
- 25 R. Caballero, M. Barrejon, J. Cerda, J. Arago, S. Seetharaman, P. de la Cruz, E. Orti, F. D'Souza and F. Langa, *J. Am. Chem. Soc.*, 2021, **143**, 11199–11208.
- 26 B. Ferrer, G. Rogez, A. Credi, R. Ballardini, M. T. Gandolfi, V. Balzani, Y. Liu, H.-R. Tseng and J. F. Stoddart, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 18411–18416.
- 27 K. Kreger, H.-W. Schmidt and R. Hildner, *Electron. Struct.*, 2021, **3**, 023001.
- 28 B. Wittmann, F. A. Wenzel, S. Wiesneth, A. T. Haedler, M. Drechsler, K. Kreger, J. Köhler, E. W. Meijer, H.-W. Schmidt and R. Hildner, *J. Am. Chem. Soc.*, 2020, **142**, 8323–8330.
- 29 *Applied Nanophotonics*, ed. H. V. Demir and S. V. Gaponenko, Cambridge University Press, Cambridge, 2018, pp. 210–226, DOI: [10.1017/9781316535868.008](https://doi.org/10.1017/9781316535868.008).
- 30 Z. Huang and X. Ma, *Cell Rep. Phys. Sci.*, 2020, **1**, 100167.
- 31 N. Yanai and N. Kimizuka, *Chem. Commun.*, 2016, **52**, 5354–5370.
- 32 H. Kouno, T. Ogawa, S. Amemori, P. Mahato, N. Yanai and N. Kimizuka, *Chem. Sci.*, 2016, **7**, 5224–5229.
- 33 P. Bharmoria, N. Yanai and N. Kimizuka, *Gels*, 2019, **5**, 18.
- 34 T. Ogawa, N. Yanai, A. Monguzzi and N. Kimizuka, *Sci. Rep.*, 2015, **5**, 10882.
- 35 A. Monguzzi, R. Tubino, S. Hoseinkhani, M. Campione and F. Meinardi, *Phys. Chem. Chem. Phys.*, 2012, **14**, 4322–4332.
- 36 T. N. Singh-Rachford and F. N. Castellano, *Coord. Chem. Rev.*, 2010, **254**, 2560–2573.
- 37 P. Duan, N. Yanai, H. Nagatomi and N. Kimizuka, *J. Am. Chem. Soc.*, 2015, **137**, 1887–1894.
- 38 S. S. Skourtis, C. Liu, P. Antoniou, A. M. Virshup and D. N. Beratan, *Proc. Natl. Acad. Sci. U. S. A.*, 2016, **113**, 8115–8120.
- 39 V. K. Praveen, C. Ranjith and N. Armaroli, *Angew. Chem., Int. Ed.*, 2014, **53**, 365–368.
- 40 Q. Zhao, Y. Chen, S.-H. Li and Y. Liu, *Chem. Commun.*, 2018, **54**, 200–203.
- 41 R. Abbel, C. Grenier, M. J. Pouderoijen, J. W. Stouwdam, P. E. Leclere, R. P. Sijbesma, E. W. Meijer and A. P. Schenning, *J. Am. Chem. Soc.*, 2009, **131**, 833–843.
- 42 G. Sun, J. Pan, Y. Wu, Y. Liu, W. Chen, Z. Zhang and J. Su, *ACS Appl. Mater. Interfaces*, 2020, **12**, 10875–10882.
- 43 T. Minami, *Bull. Chem. Soc. Jpn.*, 2021, **94**, 24–33.
- 44 K. T. Wong and D. Bassani, *NPG Asia Mater.*, 2014, **6**, e116.
- 45 F. Song, Z. Zhao, Z. Liu, J. W. Lam and B. Z. Tang, *J. Mater. Chem. C*, 2020, **8**, 3284–3301.
- 46 Z. Cai, Z. Li, S. Ravaine, M. He, Y. Song, Y. Yin, H. Zheng, J. Teng and A. Zhang, *Chem. Soc. Rev.*, 2021, **50**, 5898–5951.
- 47 Z. Wang, C. L. C. Chan, T. H. Zhao, R. M. Parker and S. Vignolini, *Adv. Opt. Mater.*, 2021, **9**, 2100519.
- 48 M. Grzelczak, J. Vermant, E. M. Furst and L. M. Liz-Marzán, *ACS Nano*, 2010, **4**, 3591–3605.
- 49 W. Wei, F. Bai and H. Fan, *Angew. Chem., Int. Ed.*, 2019, **58**, 11956–11966.
- 50 J. R. Lakowicz, *Principles of fluorescence spectroscopy*, Springer, 2006.
- 51 B. S. Richards, D. Hudry, D. Busko, A. Turshatov and I. A. Howard, *Chem. Rev.*, 2021, **121**, 9165–9195.
- 52 D. Beery, T. W. Schmidt and K. Hanson, *ACS Appl. Mater. Interfaces*, 2021, **13**, 32601–32605.
- 53 A. J. Carrod, V. Gray and K. Börjesson, *Energy Environ. Sci.*, 2022, **15**, 4982–5016.
- 54 J. C. Goldschmidt and S. Fischer, *Adv. Opt. Mater.*, 2015, **3**, 510–535.
- 55 J. Pedrini and A. Monguzzi, *J. Photonics Energy*, 2017, **8**, 022005.
- 56 J. Zhang, R. Zhang, K. Liu, Y. Li, X. Wang, X. Xie, X. Jiao and B. Tang, *Chem. Commun.*, 2021, **57**, 8320–8323.
- 57 L. Zeng, L. Huang, J. Han and G. Han, *Acc. Chem. Res.*, 2022, **55**, 2604–2615.
- 58 L. Huang and G. Han, *Small Methods*, 2018, **2**, 1700370.
- 59 S. H. Askes, A. Bahreman and S. Bonnet, *Angew. Chem.*, 2014, **126**, 1047–1051.
- 60 L. Huang, Y. Zhao, H. Zhang, K. Huang, J. Yang and G. Han, *Angew. Chem.*, 2017, **129**, 14592–14596.
- 61 T. Schloemer, P. Narayanan, Q. Zhou, E. Belliveau, M. Seitz and D. N. Congreve, *ACS Nano*, 2023, **17**, 3259–3288.
- 62 F. Auzel, *Chem. Rev.*, 2004, **104**, 139–174.
- 63 N. Yanai and N. Kimizuka, *Angew. Chem., Int. Ed.*, 2020, **59**, 10252–10264.
- 64 T. N. Singh-Rachford and F. N. Castellano, *Coord. Chem. Rev.*, 2010, **254**, 2560–2573.
- 65 C. Healy, L. Hermanspahn and P. E. Kruger, *Coord. Chem. Rev.*, 2021, **432**, 213756.
- 66 X. Ma and Y. Zhao, *Chem. Rev.*, 2015, **115**, 7794–7839.
- 67 R. Pinalli, A. Pedrini and E. Dalcanale, *Chem. Soc. Rev.*, 2018, **47**, 7006–7026.
- 68 M. J. Webber and R. Langer, *Chem. Soc. Rev.*, 2017, **46**, 6600–6620.
- 69 G. Yu, K. Jie and F. Huang, *Chem. Rev.*, 2015, **115**, 7240–7303.
- 70 R. N. Dsouza, U. Pischel and W. M. Nau, *Chem. Rev.*, 2011, **111**, 7941–7980.
- 71 C. Fan, W. Wu, J. J. Chruma, J. Zhao and C. Yang, *J. Am. Chem. Soc.*, 2016, **138**, 15405–15412.
- 72 W. Xu, W. Liang, W. Wu, C. Fan, M. Rao, D. Su, Z. Zhong and C. Yang, *Chem. – Eur. J.*, 2018, **24**, 16677–16685.



- 73 I. Roy, A. Garci, Y. Beldjoudi, R. M. Young, D. J. Pe, M. T. Nguyen, P. J. Das, M. R. Wasielewski and J. F. Stoddart, *J. Am. Chem. Soc.*, 2020, **142**, 16600–16609.
- 74 D. Asthana, S. Hisamitsu, M.-A. Morikawa, P. Duan, T. Nakashima, T. Kawai, N. Yanai and N. Kimizuka, *Org. Mater.*, 2019, **1**, 043–049.
- 75 R. Haruki, H. Kouno, M. Hosoyamada, T. Ogawa, N. Yanai and N. Kimizuka, *Chem. – Asian J.*, 2019, **14**, 1723–1728.
- 76 P. Duan, D. Asthana, T. Nakashima, T. Kawai, N. Yanai and N. Kimizuka, *Faraday Discuss.*, 2017, **196**, 305–316.
- 77 Q. Guo, G. Li, M. Rao, L. Wei, F. Gao, W. Wu, Q. Yang, G. Cheng and C. Yang, *Dyes Pigm.*, 2020, **182**, 108643.
- 78 M. Hosoyamada, N. Yanai, T. Ogawa and N. Kimizuka, *Chem. – Eur. J.*, 2016, **22**, 2060–2067.
- 79 A. Monguzzi, M. Frigoli, C. Larpent, R. Tubino and F. Meinardi, *Adv. Funct. Mater.*, 2012, **22**, 139–143.
- 80 A. Monguzzi, S. M. Borisov, J. Pedrini, I. Klimant, M. Salvalaggio, P. Biagini, F. Melchiorre, C. Lelii and F. Meinardi, *Adv. Funct. Mater.*, 2015, **25**, 5617–5624.
- 81 N. Harada, Y. Sasaki, M. Hosoyamada, N. Kimizuka and N. Yanai, *Angew. Chem., Int. Ed.*, 2021, **60**, 142–147.
- 82 S. P. Hill and K. Hanson, *J. Am. Chem. Soc.*, 2017, **139**, 10988–10991.
- 83 T. Dilbeck, S. P. Hill and K. Hanson, *J. Mater. Chem. A*, 2017, **5**, 11652–11660.
- 84 J. Pedrini, A. Monguzzi and F. Meinardi, *Phys. Chem. Chem. Phys.*, 2018, **20**, 9745–9750.
- 85 P. Bharmoria, S. Hisamitsu, H. Nagatomi, T. Ogawa, M.-A. Morikawa, N. Yanai and N. Kimizuka, *J. Am. Chem. Soc.*, 2018, **140**, 10848–10855.
- 86 H. Kouno, Y. Sasaki, N. Yanai and N. Kimizuka, *Chem. – Eur. J.*, 2019, **25**, 6124–6130.
- 87 Y. Kawashima, H. Kouno, K. Orihashi, K. Nishimura, N. Yanai and N. Kimizuka, *Mol. Syst. Des. Eng.*, 2020, **5**, 792–796.
- 88 J. Park, M. Xu, F. Li and H.-C. Zhou, *J. Am. Chem. Soc.*, 2018, **140**, 5493–5499.
- 89 B. Nordén, A. Rodger and T. Dafforn, *Linear dichroism and circular dichroism: a textbook on polarized-light spectroscopy*, Royal Society of Chemistry, 2019.
- 90 Introduction to Polarized Light, <https://www.microscopyu.com/techniques/polarized-light/introduction-to-polarized-light>.
- 91 P. C. Mondal, D. Asthana, R. K. Parashar and S. Jadhav, *Mater. Adv.*, 2021, **2**, 7620–7637.
- 92 A. Rodger and B. Nordén, *Circular dichroism and linear dichroism*, Oxford University Press, USA, 1997.
- 93 N. J. Greenfield, *Nat. Protoc.*, 2006, **1**, 2876–2890.
- 94 A. J. Miles, R. W. Janes and B. A. Wallace, *Chem. Soc. Rev.*, 2021, **50**, 8400–8413.
- 95 A. Rodger and D. Marshall, *Biochemist*, 2021, **43**, 58–64.
- 96 J. Kumar, T. Nakashima and T. Kawai, *J. Phys. Chem. Lett.*, 2015, **6**, 3445–3452.
- 97 F. S. Richardson and J. P. Riehl, *Chem. Rev.*, 1977, **77**, 773–792.
- 98 J. P. Riehl and F. S. Richardson, *Chem. Rev.*, 1986, **86**, 1–16.
- 99 J. Han, S. Guo, H. Lu, S. Liu, Q. Zhao and W. Huang, *Adv. Opt. Mater.*, 2018, **6**, 1800538.
- 100 L. Yang, J. Huang, M. Qin, X. Ma, X. Dou and C. Feng, *Nanoscale*, 2020, **12**, 6233–6238.
- 101 T. He, C. Ren, Y. Luo, Q. Wang, J. Li, X. Lin, C. Ye, W. Hu and J. Zhang, *Chem. Sci.*, 2019, **10**, 4163–4168.
- 102 S. Furumi, *Chem. Rec.*, 2010, **10**, 394–408.
- 103 A. Montali, C. Bastiaansen, P. Smith and C. Weder, *Nature*, 1998, **392**, 261–264.
- 104 B. L. Feringa and R. A. Van Delden, *Angew. Chem., Int. Ed.*, 1999, **38**, 3418–3438.
- 105 S. Suzuki, in *Circularly Polarized Luminescence of Isolated Small Organic Molecules*, ed. T. Mori, Springer Singapore, Singapore, 2020, pp. 309–325, DOI: [10.1007/978-981-15-2309-0\\_14](https://doi.org/10.1007/978-981-15-2309-0_14).
- 106 S. C. J. Meskers, *ChemPhotoChem*, 2022, **6**, e202100154.
- 107 Y. Zhang, S. Yu, B. Han, Y. Zhou, X. Zhang, X. Gao and Z. Tang, *Matter*, 2022, **5**, 837–875.
- 108 Y. Dai, J. Chen, C. Zhao, L. Feng and X. Qu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202211822.
- 109 Y. Liu and P. Xing, *Adv. Mater.*, 2023, 2300968.
- 110 N. P. M. Huck, W. F. Jager, B. de Lange and B. L. Feringa, *Science*, 1996, **273**, 1686–1688.
- 111 J. S. Kang, N. Kim, T. Kim, M. Seo and B.-S. Kim, *Macromol. Rapid Commun.*, 2022, **43**, 2100649.
- 112 J. S. Kang, S. Kang, J.-M. Suh, S. M. Park, D. K. Yoon, M. H. Lim, W. Y. Kim and M. Seo, *J. Am. Chem. Soc.*, 2022, **144**, 2657–2666.
- 113 C. Meinert, S. V. Hoffmann, P. Cassam-Chenaï, A. C. Evans, C. Giri, L. Nahon and U. J. Meierhenrich, *Angew. Chem., Int. Ed.*, 2014, **53**, 210–214.
- 114 P. K. Hashim and N. Tamaoki, *ChemPhotoChem*, 2019, **3**, 347–355.
- 115 J. S. Kang, S. Kang, J.-M. Suh, S. M. Park, D. K. Yoon, M. H. Lim, W. Y. Kim and M. Seo, *J. Am. Chem. Soc.*, 2022, **144**, 2657–2666.
- 116 Y. Deng, M. Wang, Y. Zhuang, S. Liu, W. Huang and Q. Zhao, *Light: Sci. Appl.*, 2021, **10**, 76.
- 117 E. M. Sánchez-Carnerero, A. R. Agarrabeitia, F. Moreno, B. L. Maroto, G. Muller, M. J. Ortiz and S. de la Moya, *Chem. – Eur. J.*, 2015, **21**, 13488–13500.
- 118 Y. Sang, J. Han, T. Zhao, P. Duan and M. Liu, *Adv. Mater.*, 2020, **32**, 1900110.
- 119 F. Song, Z. Zhao, Z. Liu, J. W. Y. Lam and B. Z. Tang, *J. Mater. Chem. C*, 2020, **8**, 3284–3301.
- 120 J. Zhao and P. Xing, *ChemPhotoChem*, 2022, **6**, e202100124.
- 121 Q. Li, J. Zhang, Y. Wang, G. Zhang, W. Qi, S. You, R. Su and Z. He, *Nano Lett.*, 2021, **21**, 6406–6415.
- 122 A. R. A. Palmans, J. A. J. M. Vekemans, E. E. Havinga and E. W. Meijer, *Angew. Chem., Int. Ed. Engl.*, 1997, **36**, 2648–2651.
- 123 M. M. Green, N. C. Peterson, T. Sato, A. Teramoto, R. Cook and S. Lifson, *Science*, 1995, **268**, 1860–1866.

- 124 A. R. A. Palmans and E. W. Meijer, *Angew. Chem., Int. Ed.*, 2007, **46**, 8948–8968.
- 125 M. M. J. Smulders, A. P. H. J. Schenning and E. W. Meijer, *J. Am. Chem. Soc.*, 2008, **130**, 606–611.
- 126 R. Eelkema and B. L. Feringa, *Org. Biomol. Chem.*, 2006, **4**, 3729–3745.
- 127 M. A. Mateos-Timoneda, M. Crego-Calama and D. N. Reinhoudt, *Chem. Soc. Rev.*, 2004, **33**, 363–372.
- 128 J. J. L. M. Cornelissen, A. E. Rowan, R. J. M. Nolte and N. A. J. M. Sommerdijk, *Chem. Rev.*, 2001, **101**, 4039–4070.
- 129 L. J. Prins, J. Huskens, F. de Jong, P. Timmerman and D. N. Reinhoudt, *Nature*, 1999, **398**, 498–502.
- 130 D. J. van Dijken, J. M. Beierle, M. C. A. Stuart, W. Szymański, W. R. Browne and B. L. Feringa, *Angew. Chem., Int. Ed.*, 2014, **53**, 5073–5077.
- 131 P. Duan, H. Cao, L. Zhang and M. Liu, *Soft Matter*, 2014, **10**, 5428–5448.
- 132 L. Zhang, L. Qin, X. Wang, H. Cao and M. Liu, *Adv. Mater.*, 2014, **26**, 6959–6964.
- 133 S. Huang, H. Yu and Q. Li, *Adv. Sci.*, 2021, **8**, 2002132.
- 134 A. E. Rowan and R. J. M. Nolte, *Angew. Chem., Int. Ed.*, 1998, **37**, 63–68.
- 135 D. K. Smith, *Chem. Soc. Rev.*, 2009, **38**, 684–694.
- 136 M. Liu, L. Zhang and T. Wang, *Chem. Rev.*, 2015, **115**, 7304–7397.
- 137 C. Liu, J.-C. Yang, J. W. Y. Lam, H.-T. Feng and B. Z. Tang, *Chem. Sci.*, 2022, **13**, 611–632.
- 138 Y. Sang, D. Yang, Z. Shen, P. Duan and M. Liu, *J. Phys. Chem. C*, 2020, **124**, 17274–17281.
- 139 M. Zhou, Y. Sang, X. Jin, S. Chen, J. Guo, P. Duan and M. Liu, *ACS Nano*, 2021, **15**, 2753–2761.
- 140 Q. Jiang, X. Xu, P.-A. Yin, K. Ma, Y. Zhen, P. Duan, Q. Peng, W.-Q. Chen and B. Ding, *J. Am. Chem. Soc.*, 2019, **141**, 9490–9494.
- 141 B.-C. Kim, H.-J. Choi, J.-J. Lee, F. Araoka and S.-W. Choi, *Adv. Funct. Mater.*, 2019, **29**, 1903246.
- 142 T. Li, H. Guo, Y. Wang, G. Ouyang, Q.-Q. Wang and M. Liu, *Chem. Commun.*, 2021, **57**, 13554–13557.
- 143 K. Q. Le, S. Hashiyada, M. Kondo and H. Okamoto, *J. Phys. Chem. C*, 2018, **122**, 24924–24932.
- 144 K. Yang, S. Ma, Y. Wu, B. Zhao and J. Deng, *Chem. Mater.*, 2023, **35**, 1273–1282.
- 145 Z.-W. Luo, A. Huang, H.-Y. Luo, J.-K. Chen, J. Huang and H.-L. Xie, *Macromolecules*, 2023, **56**, 2700–2708.
- 146 Y. Bao, G. Zhang, N. Wang, M. Pan and W. Zhang, *J. Mater. Chem. C*, 2023, **11**, 2475–2479.
- 147 J. Wade, J. R. Brandt, D. Reger, F. Zinna, K. Y. Amsharov, N. Jux, D. L. Andrews and M. J. Fuchter, *Angew. Chem., Int. Ed.*, 2021, **60**, 222–227.
- 148 K. S. Park, Z. Xue, B. B. Patel, H. An, J. J. Kwok, P. Kafle, Q. Chen, D. Shukla and Y. Diao, *Nat. Commun.*, 2022, **13**, 2738.
- 149 J. Zhang, J. Hao, Y. Wei, F. Xiao, P. Yin and L. Wang, *J. Am. Chem. Soc.*, 2010, **132**, 14–15.
- 150 L.-J. Chen, H.-B. Yang and M. Shionoya, *Chem. Soc. Rev.*, 2017, **46**, 2555–2576.
- 151 H. Cao, Q. Yuan, X. Zhu, Y.-P. Zhao and M. Liu, *Langmuir*, 2012, **28**, 15410–15417.
- 152 B. Chang, X. Li and T. Sun, *Eur. Polym. J.*, 2019, **118**, 365–381.
- 153 H. Song, H. Zhu, Z. Huang, Y. Zhang, W. Zhao, J. Liu, Q. Chen, C. Yin, L. Xing, Z. Peng, P. Liao, Y. Wang, Y. Wang and K. Wu, *ACS Nano*, 2019, **13**, 7202–7208.
- 154 Z. Cheng and M. R. Jones, *Nat. Commun.*, 2022, **13**, 4207.
- 155 S. Kikkawa, M. Okayasu, H. Hikawa and I. Azumaya, *Cryst. Growth Des.*, 2021, **21**, 1148–1158.
- 156 W. Shang, X. Zhu, T. Liang, C. Du, L. Hu, T. Li and M. Liu, *Angew. Chem., Int. Ed.*, 2020, **59**, 12811–12816.
- 157 W. Yang, X. Chai, L. Chi, X. Liu, Y. Cao, R. Lu, Y. Jiang, X. Tang, H. Fuchs and T. Li, *Chem. – Eur. J.*, 1999, **5**, 1144–1149.
- 158 Anuradha, D. D. La, M. Al Kobaisi and S. V. Bhosale, *Sci. Rep.*, 2015, **5**, 15652.
- 159 S. Pakhomov, R. P. Hammer, B. K. Mishra and B. N. Thomas, *Proc. Natl. Acad. Sci. U. S. A.*, 2003, **100**, 3040–3042.
- 160 E. Yashima, N. Ousaka, D. Taura, K. Shimomura, T. Ikai and K. Maeda, *Chem. Rev.*, 2016, **116**, 13752–13990.
- 161 E. R. Zubarev, M. U. Pralle, E. D. Sone and S. I. Stupp, *J. Am. Chem. Soc.*, 2001, **123**, 4105–4106.
- 162 D. Asthana, J. Shukla, S. Dana, V. Rani, M. R. Ajayakumar, K. Rawat, K. Mandal, P. Yadav, S. Ghosh and P. Mukhopadhyay, *Chem. Commun.*, 2015, **51**, 15237–15240.
- 163 G. Zhang, X. Cheng, Y. Wang and W. Zhang, *Aggregate*, 2023, **4**, e262.
- 164 S.-Y. Yu, Z.-X. Zhang, E. C.-C. Cheng, Y.-Z. Li, V. W.-W. Yam, H.-P. Huang and R. Zhang, *J. Am. Chem. Soc.*, 2005, **127**, 17994–17995.
- 165 L. Caswell, M. A. Garcia-Garibay, J. R. Scheffer and J. Trotter, *J. Chem. Educ.*, 1993, **70**, 785.
- 166 J. Zhao, T. Zhang, X.-Y. Dong, M.-E. Sun, C. Zhang, X. Li, Y. S. Zhao and S.-Q. Zang, *J. Am. Chem. Soc.*, 2019, **141**, 15755–15760.
- 167 S. Kirschner and K. R. Magnell, in *Werner Centennial*, American chemical society, 1967, vol. 62, ch. 24, pp. 366–377.
- 168 G. Park, H. Kim, H. Yang, K. R. Park, I. Song, J. H. Oh, C. Kim and Y. You, *Chem. Sci.*, 2019, **10**, 1294–1301.
- 169 S. Sato, T. Murase and M. Fujita, in *Supramol. Chem*, 2012, DOI: [10.1002/9780470661345.smc078](https://doi.org/10.1002/9780470661345.smc078).
- 170 M. Han, D. M. Engelhard and G. H. Clever, *Chem. Soc. Rev.*, 2014, **43**, 1848–1860.
- 171 R. Chakrabarty, P. S. Mukherjee and P. J. Stang, *Chem. Rev.*, 2011, **111**, 6810–6918.
- 172 F. Hof, S. L. Craig, C. Nuckolls and J. Rebek, Jr., *Angew. Chem., Int. Ed.*, 2002, **41**, 1488–1508.
- 173 A. B. Grommet, L. M. Lee and R. Klajn, *Acc. Chem. Res.*, 2020, **53**, 2600–2610.
- 174 A. B. Grommet, M. Feller and R. Klajn, *Nat. Nanotechnol.*, 2020, **15**, 256–271.
- 175 R. Ham, C. J. Nielsen, S. Pullen and J. N. H. Reek, *Chem. Rev.*, 2023, **123**, 5225–5261.

- 176 F. Zhang, J. Nangreave, Y. Liu and H. Yan, *J. Am. Chem. Soc.*, 2014, **136**, 11198–11211.
- 177 N. C. Seeman and H. F. Sleiman, *Nat. Rev. Mater.*, 2017, **3**, 17068.
- 178 F. Hong, F. Zhang, Y. Liu and H. Yan, *Chem. Rev.*, 2017, **117**, 12584–12640.
- 179 Q. Li, Y. Wang, G. Zhang, R. Su and W. Qi, *Chem. Soc. Rev.*, 2023, **52**, 1549–1590.
- 180 L. Li, S. Nie, T. Du, J. Zhao and X. Chen, *MedComm – Biomaterials and Applications*, 2023, vol. 2, p. e37.
- 181 M. Endo, Y. Yang and H. Sugiyama, *Biomater. Sci.*, 2013, **1**, 347–360.
- 182 P. Zhan, A. Peil, Q. Jiang, D. Wang, S. Mousavi, Q. Xiong, Q. Shen, Y. Shang, B. Ding, C. Lin, Y. Ke and N. Liu, *Chem. Rev.*, 2023, **123**, 3976–4050.