

Cite this: *Chem. Sci.*, 2023, 14, 1861 All publication charges for this article have been paid for by the Royal Society of Chemistry

# Dynamic charge collecting mechanisms of cobalt phosphate on hematite photoanodes studied by photoinduced absorption spectroscopy†

Dongfeng Li,<sup>ab</sup> Ruifang Wei,<sup>ac</sup> Heng Yin,<sup>a</sup> Hemin Zhang,<sup>d</sup> Xiuli Wang<sup>id</sup>\*<sup>a</sup> and Can Li<sup>id</sup>\*<sup>abc</sup>

Reaction sites, surface states, and surface loaded electrocatalysts are photoinduced charge storage sites and critical to photoelectrochemical (PEC) performance, however the charge transfer mechanisms involved in the three remain poorly understood. Herein, we studied the charge transfer processes in hematite (Fe<sub>2</sub>O<sub>3</sub>) without/with loaded cobalt phosphate (CoPi) by *operando* photoinduced absorption (PIA) spectroscopy. The loaded CoPi receives trapped holes in surface states at low potential and directly captures holes in the valence band at high potential. Through the dynamic hole storage mechanisms, loaded CoPi on Fe<sub>2</sub>O<sub>3</sub> facilitates spatial charge separation and serves as a charge transfer mediator, instead of serving as a catalyst to change the water oxidation mechanism (constant third-order reaction). The spatial separation of photoinduced charges between Fe<sub>2</sub>O<sub>3</sub> and CoPi results in more long-lived holes on the Fe<sub>2</sub>O<sub>3</sub> surface to improve PEC water oxidation kinetically. The dynamic charge collecting mechanism sheds light on the understanding and designing of electrocatalyst loaded photoanodes.

Received 20th October 2022

Accepted 19th January 2023

DOI: 10.1039/d2sc05802b

[rsc.li/chemical-science](https://rsc.li/chemical-science)

## Introduction

Photoelectrochemical (PEC) water splitting is a promising strategy to convert solar energy into clean hydrogen fuel.<sup>1</sup> In PEC water splitting, the water oxidation process by a photoanode is generally regarded as a bottleneck and strongly relies on the surface hole density, which is related to various hole storage sites.<sup>2–4</sup> A high-performance photoanode is usually composed of a conductive back contact, light-absorbing semiconductor and surface loaded electrocatalyst. The multiple interfaces (semiconductor|electrocatalyst, semiconductor|solution, and electrocatalyst|solution) and charge storage sites (reaction sites, surface states of the photoanode, and the loaded electrocatalyst) complicate the surface reaction mechanisms.<sup>5,6</sup> Therefore, understanding the charge transfer mechanisms among reaction sites, surface

states of the photoanode and the loaded electrocatalyst in photoelectrocatalysis is critical.

Among various photoanodes, hematite (Fe<sub>2</sub>O<sub>3</sub>) has received lots of attention owing to its abundant, nontoxic and scalable characteristics.<sup>7,8</sup> There have been many research studies on revealing hole storage sites related to PEC properties in the bare Fe<sub>2</sub>O<sub>3</sub> system, including reaction intermediates,<sup>9–11</sup> multi-hole cooperation clusters<sup>4,12</sup> and filling surface trap states.<sup>13</sup> In order to promote PEC performances, the OER catalysts, such as cobalt phosphate (CoPi)<sup>14</sup> and NiFe(OH)<sub>x</sub> electrocatalysts,<sup>15–17</sup> are usually loaded on the Fe<sub>2</sub>O<sub>3</sub> surface as new hole storage sites. The loaded electrocatalyst negatively shifts the onset potential and improves the photocurrent, while it definitely influences or fully changes the properties of hole storage sites resulting in complicated charge transfer processes. In particular, the promoted role of the electrocatalyst on the Fe<sub>2</sub>O<sub>3</sub> surface is a subject of debate, particularly CoPi, a common and effective covering layer.<sup>6,14,18–21</sup> There appear two opposite explanations about the role of CoPi including a catalyst and spectator by (photo)electrochemical and spectroscopic techniques.<sup>18,22,23</sup> Boettcher claimed that potential-sensing electrochemical atomic force microscopy (AFM) in *operando* gave the direct evidence of loaded CoPi as a catalyst by tracking surface potential variation of CoPi in photoelectrocatalysis.<sup>18–20</sup> Nevertheless, *in situ* spectroscopy likewise offered direct proof of the CoPi layer as a spectator through similar spectra shapes and charge transfer dynamics regardless of transient or steady state spectroscopy.<sup>14,24–26</sup> Furthermore, spectroscopic results also revealed a crucial point that the contribution of the CoPi

<sup>a</sup>State Key Laboratory of Catalysis, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian National Laboratory for Clean Energy, Dalian 116023, China. E-mail: canli@dicp.ac.cn; xiuliwang@dicp.ac.cn

<sup>b</sup>University of Chinese Academy of Sciences, Beijing, 100049, China

<sup>c</sup>Department of Chemical Physics, University of Science and Technology of China, Hefei 230026, China

<sup>d</sup>College of Materials Science and Engineering, Sichuan University, Engineering Research Center of Alternative Energy Materials and Devices, Ministry of Education, Chengdu 610065, China

† Electronic supplementary information (ESI) available: Detailed experimental section and characterization methods. See DOI: <https://doi.org/10.1039/d2sc05802b>



layer to photocurrent was lower than 5%.<sup>22</sup> However, these research studies were mainly devoted to revealing the reaction sites of the water oxidation reaction of Fe<sub>2</sub>O<sub>3</sub> modified with an electrocatalyst and ignore interfacial dynamic processes.

In principle, both the surface states of Fe<sub>2</sub>O<sub>3</sub> and loaded electrocatalyst will compete for photoinduced holes with reaction sites on the photoanode surface. The reduction reaction of photoinduced holes by surface states or the electrocatalyst is dependent on their thermodynamic driving force, and should show distinct dynamics/kinetics. Generally, compared with free holes in the valence band (VB), the trapped holes in surface states possess a lower PEC activity and tend to recombine with photoinduced electrons. If the loaded electrocatalyst plays a leading role in surface catalysis, a surface reaction kinetics similar to electrocatalysis is expected, *vice versa*. But whether the trapped holes interact with the loaded electrocatalyst and its role in photoelectrocatalysis is unclear. More importantly, it is also not studied whether there is charge transfer between the loaded electrocatalyst and reaction sites of Fe<sub>2</sub>O<sub>3</sub> and its crucial roles if loaded electrocatalysts do not serve as a catalyst. Thus, the dynamic interaction between the electrocatalyst and Fe<sub>2</sub>O<sub>3</sub> and its role in PEC performances are quite important and deserve to be studied deeply.

In this work, the charge transfer processes among surface states, reaction sites and the coated electrocatalyst for Fe<sub>2</sub>O<sub>3</sub> without/with CoPi loading were studied by photoinduced absorption (PIA) spectroscopy. Loaded CoPi on the Fe<sub>2</sub>O<sub>3</sub> surface does not remove the mid-gap surface states. The

dynamic transition in collecting holes for loaded CoPi from surface states to the VB following increasing potential is discussed. The roles of the dynamic charge collecting mechanism in PEC water oxidation are revealed. This dynamic mechanism sheds light on the understanding and designing of electrocatalyst loaded photoanodes.

## Results and discussion

### Determining the distribution of surface states in bare Fe<sub>2</sub>O<sub>3</sub> and CoPi/Fe<sub>2</sub>O<sub>3</sub>

Fe<sub>2</sub>O<sub>3</sub> photoanodes were prepared by a combined method of solvothermal and high-temperature calcination.<sup>27</sup> A subsequent electrodeposition was applied to obtain CoPi/Fe<sub>2</sub>O<sub>3</sub> photoanodes.<sup>14</sup> The cyclic voltammetry (CV) curve of CoPi/Fe<sub>2</sub>O<sub>3</sub> shows negligible current at the applied bias of 0.6–1.6 V vs. RHE in the dark (Fig. S1†), while the CV curve of CoPi displays obvious current for cobalt oxidation or water oxidation. The negligible current of CoPi/Fe<sub>2</sub>O<sub>3</sub> suggests a dense and non-porous Fe<sub>2</sub>O<sub>3</sub> film.<sup>16</sup> For the PEC performances, loaded CoPi on the Fe<sub>2</sub>O<sub>3</sub> surface negatively shifts onset potential, improves photocurrent, and enhances transient spikes (Fig. 1a and b), in line with previous reports.<sup>14,23,28</sup>

In order to determine the charge transfer processes among reaction sites, surface states and the surface loaded electrocatalyst, the potential distribution of mid-gap or surface states is first investigated by electrochemical impedance spectroscopy (EIS) under illumination and in the dark. The EIS results (Fig. 1c and d) fitted with the equivalent circuit (Fig. S2†)

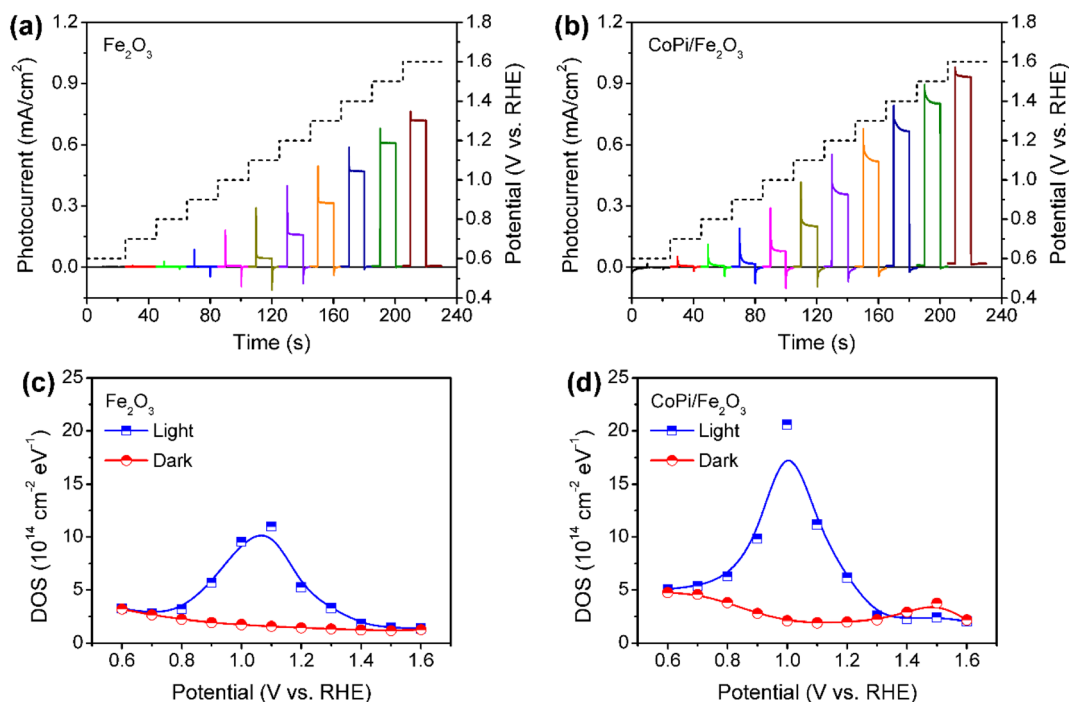


Fig. 1 Potential-dependent transient photocurrents for (a) bare Fe<sub>2</sub>O<sub>3</sub> and (b) CoPi/Fe<sub>2</sub>O<sub>3</sub> photoanodes under chopped illumination (AM 1.5 G: 100 mW cm<sup>-2</sup>). The applied potential is shown by a dashed line in the right axis. DOS of surface states in (c) bare Fe<sub>2</sub>O<sub>3</sub> and (d) CoPi/Fe<sub>2</sub>O<sub>3</sub> as a function of potential under illumination (456 nm LED: 5 mW cm<sup>-2</sup>) and in the dark.



show that bare  $\text{Fe}_2\text{O}_3$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanodes exhibit a similar distribution of density of states ( $\text{DOS} = C/e$ , where  $C$  is the capacitance and  $e$  is the elementary charge.) in the 0.7–1.4  $V_{\text{RHE}}$  range. Loading  $\text{CoPi}$  on the  $\text{Fe}_2\text{O}_3$  surface shifts the distribution of surface states about 100 meV towards lower potential. Moreover, CV results in Fig. S3† after PEC water oxidation also display similar reduction waves in the 0.8–1.4  $V_{\text{RHE}}$  range for bare  $\text{Fe}_2\text{O}_3$  or in the 0.6–1.1  $V_{\text{RHE}}$  range for  $\text{CoPi}/\text{Fe}_2\text{O}_3$ . Both EIS and CV results demonstrate that there are similar distributions of surface states in bare  $\text{Fe}_2\text{O}_3$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanodes in the 0.8–1.4  $V_{\text{RHE}}$  range. Therefore, although loading  $\text{CoPi}$  eliminates fractional surface states and releases Fermi-level pinning revealed by fast decay in chopped OCP results (Fig. S4†), the surface states in the 0.8–1.4  $V_{\text{RHE}}$  range still exist in  $\text{CoPi}/\text{Fe}_2\text{O}_3$ .

The surface states in  $\text{Fe}_2\text{O}_3$  always act as hole trap states and have been described as water oxidation intermediates<sup>9,11</sup> or recombination sites,<sup>29</sup> because  $\text{Fe}_2\text{O}_3$  is an n-type semiconductor with a Fermi level close to the conduction band (CB) edge. Thus, the surface states in the 0.8–1.4  $V_{\text{RHE}}$  range are tentatively assigned as hole trap states for both bare  $\text{Fe}_2\text{O}_3$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanodes. In principle, with the existence of surface states, the photoinduced holes in the VB might be consumed by indirect paths (water oxidation by trapped holes:  $h^+_{\text{surface states}} + \text{H}_2\text{O} \rightarrow \text{O}_2$ , or trap-mediated recombination) for bare  $\text{Fe}_2\text{O}_3$ , besides direct paths (water

oxidation by VB holes:  $h^+_{\text{VB}} + \text{H}_2\text{O} \rightarrow \text{O}_2$ , or recombination). When  $\text{CoPi}$  is loaded on  $\text{Fe}_2\text{O}_3$ , the surface states can bring new charge transfer paths between the photoinduced holes, surface states and the loaded  $\text{CoPi}$ . Namely, the photoinduced holes in  $\text{Fe}_2\text{O}_3$  can move to  $\text{CoPi}$  *via* surface states (sequential hole transfer) besides the direct transfer of VB holes to  $\text{CoPi}$ , which may play a vital role in  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoelectrocatalysis.

### Charging sites of $\text{CoPi}/\text{Fe}_2\text{O}_3$ at low and high potentials

Next, the photoinduced charge transfer processes were studied to reveal the direct or sequential hole transfer processes in  $\text{CoPi}/\text{Fe}_2\text{O}_3$  with the existence of surface states. Based on the position of the energy levels, the oxidation ability of trapped holes (surface states: 0.8–1.4  $V_{\text{RHE}}$ ) should be lower than that of free holes (VB: 2.5  $V_{\text{RHE}}$ ). A logical speculation is that a probe with <1.4  $V_{\text{RHE}}$  redox potential can be oxidized by trapped holes, otherwise there will be no oxidation as schematically shown in Fig. 2a. Thus,  $\text{CoPi}$  ( $\text{Co}^{2+/3+}$ :  $\sim 1.10 V_{\text{RHE}}$ ) and  $\text{NiOOH}$  ( $\text{Ni}^{2+/3+}$ :  $\sim 1.38 V_{\text{RHE}}$ ) electrocatalysts were chosen as probes and deposited on the  $\text{Fe}_2\text{O}_3$  surface (Fig. 2b). The role of surface states in charge transfer was first studied by PIA spectroscopy at low potential (0.8  $V_{\text{RHE}}$ ). The wavelength-dependent PIA responses of  $\text{CoPi}$ , bare  $\text{Fe}_2\text{O}_3$ ,  $\text{CoPi}/\text{Fe}_2\text{O}_3$  and  $\text{NiOOH}/\text{Fe}_2\text{O}_3$  at 0.8  $V_{\text{RHE}}$  are shown in Fig. 2c. Bare  $\text{Fe}_2\text{O}_3$  and  $\text{CoPi}$  display negligible PIA intensity, illustrating that the bulk/surface recombination is too fast to probe. In contrast,  $\text{CoPi}/\text{Fe}_2\text{O}_3$  presents an appreciable

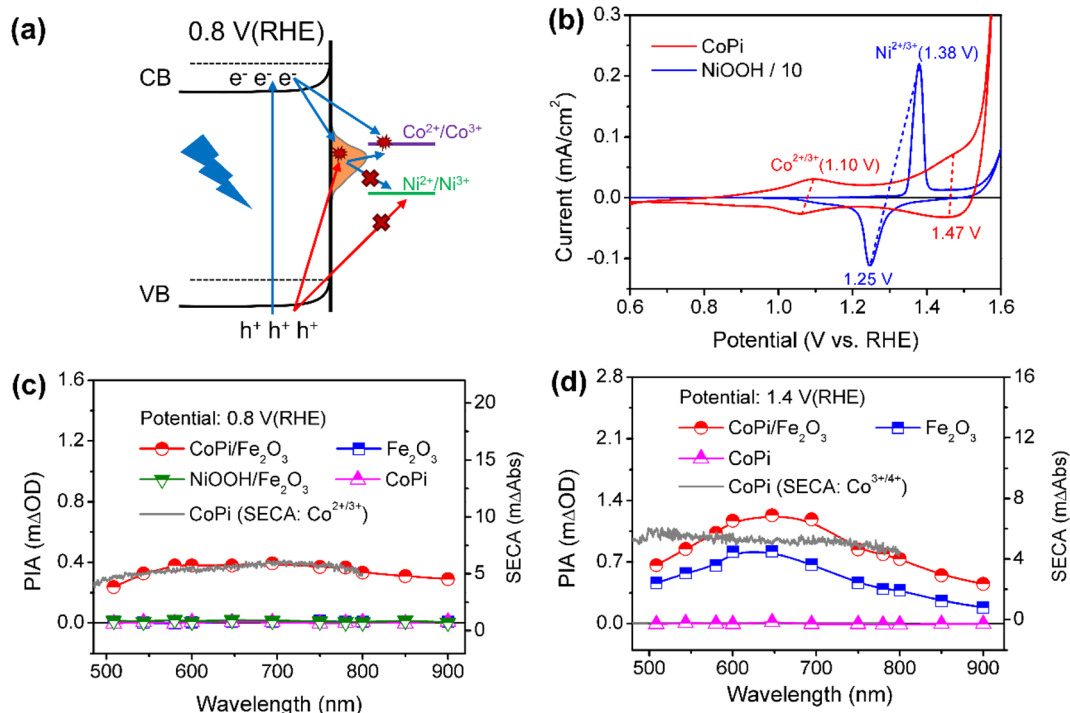


Fig. 2 (a) Schematic of charge transfer between surface states and probes. Red and blue arrows refer to the transfer processes of photoinduced holes and electrons, respectively. 'x' denotes no charge transfer. (b) CV and corresponding redox potentials of  $\text{CoPi}$  and  $\text{NiOOH}$ . (c) Wavelength-dependent PIA spectra of bare  $\text{Fe}_2\text{O}_3$ ,  $\text{CoPi}$ ,  $\text{CoPi}/\text{Fe}_2\text{O}_3$  and  $\text{NiOOH}/\text{Fe}_2\text{O}_3$  at low potential of 0.8  $V_{\text{RHE}}$ ; left axis is PIA spectra and right axis is the SECA spectrum of  $\text{CoPi}$  ( $\text{Co}^{2+/3+}$ : 1.3  $V_{\text{RHE}}$  – 1.0  $V_{\text{RHE}}$ ). (d) Wavelength-dependent PIA spectra of bare  $\text{Fe}_2\text{O}_3$ ,  $\text{CoPi}$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$  at high potential of 1.4  $V_{\text{RHE}}$ ; left axis is PIA spectra and right axis is the SECA spectrum of  $\text{CoPi}$  ( $\text{Co}^{3+/4+}$ : 1.7  $V_{\text{RHE}}$  – 1.4  $V_{\text{RHE}}$ ). Pump wavelength in PIA is 456 nm ( $5 \text{ mW cm}^{-2}$ ).



PIA intensity, indicating the effective hole transfer from  $\text{Fe}_2\text{O}_3$  to CoPi. Moreover, the coexistence of PIA spectra of CoPi/ $\text{Fe}_2\text{O}_3$  and spectroelectrochemical absorption (SECA) spectra of CoPi ( $\text{Co}^{2+/3+}$ , for calculation details, see Fig. S5†) in Fig. 2c indicates that CoPi is the main hole storage site at  $0.8 V_{\text{RHE}}$ . Amazingly, no PIA response is observed in  $\text{NiOOH}/\text{Fe}_2\text{O}_3$  at  $0.8 V_{\text{RHE}}$ , corresponding to no hole transfer from  $\text{Fe}_2\text{O}_3$  to  $\text{NiOOH}$  and in line with negligible photocurrent in Fig. S6.† Since free holes in the VB of  $\text{Fe}_2\text{O}_3$  can oxidize both CoPi and  $\text{NiOOH}$ , the distinct PIA response should result from the CoPi oxidation by the long-lived trapped holes in the surface states of  $\text{Fe}_2\text{O}_3$ . Thus, at low potential, the photoinduced holes in  $\text{Fe}_2\text{O}_3$  mainly undergo sequential transfer processes from the VB to surface states then to CoPi. The spatial separation between holes in CoPi and electrons in  $\text{Fe}_2\text{O}_3$  prolongs charge lifetimes (Fig. S7†) by suppressing charge recombination at  $0.8 V_{\text{RHE}}$ . Moreover, transient absorption spectra of CoPi/ $\text{Fe}_2\text{O}_3$  at 100 ms at  $0.8 V_{\text{RHE}}$  in Fig. S7e† display a broad absorption which is quite similar to the absorption spectra of oxidized  $\text{Co}^{3+}$ , demonstrating that the long-lived transient absorption signals in CoPi/ $\text{Fe}_2\text{O}_3$  at lower potential should originate from cobalt oxidation of  $\text{Co}^{2+/3+}$  rather than passivating surface states or increasing band-bending.<sup>14</sup> A combination of negligible photocurrent (Fig. 1b) and appreciable PIA (Fig. 2c) at  $0.8 V_{\text{RHE}}$  demonstrates that the oxidized CoPi cannot contribute to the water oxidation processes. Therefore, at low potential, the loaded CoPi on the  $\text{Fe}_2\text{O}_3$  surface serves as the charging site for photoinduced holes, and prolongs the lifetime of holes by suppressing recombination, but with no catalysis effect for water oxidation.

Then, the charge transfer processes were studied by PIA spectroscopy at high potential of  $1.4 V_{\text{RHE}}$  to reveal the main charging sites during the OER. In wavelength-dependent PIA spectra (Fig. 2d), bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  display similar spectral shapes from 500 to 900 nm, while CoPi still shows no photo-response. The PIA spectra shape is in line with the absorption spectra of photoinduced holes in  $\text{Fe}_2\text{O}_3$  and different from absorption properties of oxidized cobalt species in CoPi ( $\text{Co}^{2+/3+}$  shown in Fig. 2c and  $\text{Co}^{3+/4+}$  shown in Fig. 2d).<sup>12,29,30</sup> These results suggest that the charging sites of bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes at high potential ( $1.4 V_{\text{RHE}}$ ) may be mainly on the  $\text{Fe}_2\text{O}_3$  surface. Moreover, the similar transient absorption results of bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes further confirm the assignment of same charging sites (Fig. S8†).<sup>14,24</sup>

Besides the spectral shape, an obvious increase of PIA amplitude for CoPi/ $\text{Fe}_2\text{O}_3$  is observed relative to that of  $\text{Fe}_2\text{O}_3$  in Fig. 2d. In order to uncover the origin of the increased PIA amplitude, a quantitative comparison of ratios of PIA amplitudes ( $\text{PIA}_{\text{CoPi}/\text{Fe}_2\text{O}_3}/\text{PIA}_{\text{Fe}_2\text{O}_3} \geq 1.8$ ) and photocurrents ( $J_{\text{CoPi}/\text{Fe}_2\text{O}_3}/J_{\text{Fe}_2\text{O}_3} \sim 1.8$ ) for the  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes is displayed in Figs. S8a† and S8b. The ratios display the proportional relationship between photocurrent and hole density ( $J \propto [h^+]$ ). However, CoPi/ $\text{Fe}_2\text{O}_3$  at this potential ( $1.4 V_{\text{RHE}}$ ) and illumination ( $5 \text{ mW cm}^{-2}$ ) displays a third-order kinetics ( $J \propto [h^+]^3$ ) which will be further discussed in detail below, suggesting that the increased PIA amplitude should lead to a much higher ratio of photocurrents ( $1.83^3 \approx 5.8$ ). This

disagreement indicates that the increased PIA amplitude is not only derived from the increased holes in  $\text{Fe}_2\text{O}_3$ , but also from the effective hole storage in loaded CoPi. Since the PIA data are obtained from quasi-steady-state PIA spectra measured with a continuous pulsed light on, the initial states of cobalt ions in CoPi/ $\text{Fe}_2\text{O}_3$  for PIA at  $1.4 V_{\text{RHE}}$  should be the  $\text{Co}^{3+}$  state due to the sequential and direct hole transfer processes (Fig. S9c†). The increased PIA amplitude in CoPi/ $\text{Fe}_2\text{O}_3$  (Fig. 2d) is derived from the oxidation process of  $\text{Co}^{3+/4+}$  by photoinduced holes in the VB of  $\text{Fe}_2\text{O}_3$  besides increased holes in  $\text{Fe}_2\text{O}_3$ , since the trapped holes in surface states cannot oxidize  $\text{Co}^{3+/4+}$  (redox potential:  $1.47 V_{\text{RHE}}$ ). The  $\text{Co}^{3+/4+}$  oxidation process *via* direct hole transfer contributes little to the photocurrent of CoPi/ $\text{Fe}_2\text{O}_3$  at  $1.4 V_{\text{RHE}}$ , which should be less than  $\sim 1 \mu\text{A}$  by evaluation from the PIA amplitude in the  $I-t$  curve in Fig. S10.† Loaded CoPi on the  $\text{Fe}_2\text{O}_3$  surface still exhibits negligible catalysis at high potential. Therefore, at high potential ( $1.4 V_{\text{RHE}}$ ), the main charging sites of photoinduced holes in the CoPi/ $\text{Fe}_2\text{O}_3$  photoanode are the reaction sites on the  $\text{Fe}_2\text{O}_3$  surface and  $\text{Co}^{3+/4+}$  in the CoPi electrocatalyst. Moreover, the same as that at low potential ( $0.8 V_{\text{RHE}}$ ), the spatial separation between holes in CoPi and electrons in  $\text{Fe}_2\text{O}_3$  also prolongs charge lifetimes by suppressing charge recombination (Fig. S11†) at high potential ( $1.4 V_{\text{RHE}}$ ).

### Potentiodynamic charge storage processes

Wavelength-dependent PIA spectra of bare  $\text{Fe}_2\text{O}_3$ , CoPi and CoPi/ $\text{Fe}_2\text{O}_3$  demonstrate that loaded CoPi displays two distinct hole-storage mechanisms, where loaded CoPi on the  $\text{Fe}_2\text{O}_3$  surface receives trapped holes in surface states and free holes in the VB at low and high potentials, respectively. In order to further uncover potential-dependent charge storage mechanisms, the PIA spectra were recorded at a fixed probe wavelength and varying potentials ( $0.6 V_{\text{RHE}} \leq \text{potential} \leq 1.6 V_{\text{RHE}}$ ). Since the probe wavelength of  $> 650 \text{ nm}$  in PIA spectra has been assigned to photoinduced holes on the  $\text{Fe}_2\text{O}_3$  surface by the hole scavenger and potential-dependent TAS experiments (Fig. S8†),<sup>15,31</sup> the probe wavelength of  $694.3 \text{ nm}$  was used to monitor photoinduced hole dynamics on the  $\text{Fe}_2\text{O}_3$  surface. The reasonability is confirmed by the linear relationship of PIA intensity and photoinduced hole density in  $\text{Fe}_2\text{O}_3$  in Fig. S10.† Moreover, the linear relationship between absorbance and high-valent cobalt species (holes) in Fig. S9† demonstrates that the probe wavelength of  $694.3 \text{ nm}$  is also suitable for monitoring holes in CoPi.

Fig. 3a–c show the potential-dependent PIA spectra of bare  $\text{Fe}_2\text{O}_3$ , CoPi and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes. There are three regions for a PIA spectrum, including baseline in the dark ( $0-0.5 \text{ s}$ ), photoinduced species accumulation ( $0.5-6 \text{ s}$ ) and species consumption after turning the light off ( $6-10 \text{ s}$ ). The variation trend of PIA amplitudes with applied potential is extracted and shown in Fig. 3d. CoPi shows no PIA response at  $0.6-1.6 V_{\text{RHE}}$ , suggesting that PEC charging of CoPi is only through collecting extraneous charges from  $\text{Fe}_2\text{O}_3$ . For the bare  $\text{Fe}_2\text{O}_3$  photoanode, the PIA amplitudes increase monotonically to a saturation intensity. The invariable PIA intensity above  $1.2 V_{\text{RHE}}$  can



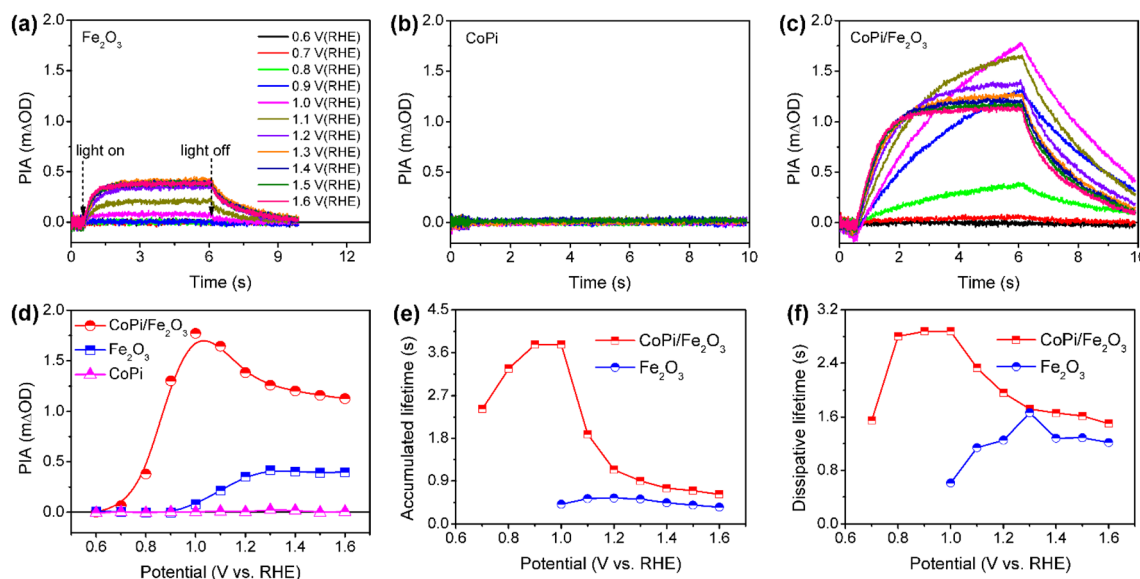


Fig. 3 PIA responses at various potentials for bare  $\text{Fe}_2\text{O}_3$  (a), CoPi (b) and CoPi/ $\text{Fe}_2\text{O}_3$  (c). (d) PIA amplitudes following increasing potential extracted from Fig. 2a–2c. Average lifetimes ( $\tau_{\text{ave}}$ ) of (e) accumulated and (f) dissipative processes for bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes in (a and c). Pump wavelength is 456 nm ( $5 \text{ mW cm}^{-2}$ ); probe wavelength is 694.3 nm; colors of curves at different potentials in (a–c) are identical.

originate from the signal overlap of inactive holes (surface states) and active holes (VB), which is a common phenomenon for the  $\text{Fe}_2\text{O}_3$  photoanode by the solvothermal method.<sup>29</sup> Increasing the external potential results in higher percentage of active holes, but doesn't influence PIA intensity. However, potential-dependent PIA amplitudes of CoPi/ $\text{Fe}_2\text{O}_3$  display a complicated trend, first increasing (0.7–1.0  $V_{\text{RHE}}$ ) and then decreasing (1.0–1.6  $V_{\text{RHE}}$ ) resulting in a peak at 1.0  $V_{\text{RHE}}$ . Moreover, at the same potential, the PIA amplitudes of CoPi/ $\text{Fe}_2\text{O}_3$  are greater than those of bare  $\text{Fe}_2\text{O}_3$ . Because the extinction coefficients of  $\text{Co}^{2+}/\text{Co}^{3+}$  ( $\epsilon_1 = 7332 \text{ M}^{-1} \text{ cm}^{-1}$ ) and  $\text{Co}^{3+}/\text{Co}^{4+}$  ( $\epsilon_2 = 1833 \text{ M}^{-1} \text{ cm}^{-1}$ ) in CoPi are larger than the extinction coefficient of photoinduced holes ( $\epsilon = 637 \text{ M}^{-1} \text{ cm}^{-1}$ ) in bare  $\text{Fe}_2\text{O}_3$  (Fig. S10<sup>†</sup>), the increased PIA amplitude in the whole applied potential range (0.6–1.6  $V_{\text{RHE}}$ ) should originate from hole transfer from the  $\text{Fe}_2\text{O}_3$  surface to CoPi. Combined with all PIA results in Fig. 2 and 3, the complicated variation of PIA amplitudes in CoPi/ $\text{Fe}_2\text{O}_3$  can be attributed to the transition from oxidation of  $\text{Co}^{2+}/\text{Co}^{3+}$  by trapped holes in surface states at low potentials to oxidation of  $\text{Co}^{3+}/\text{Co}^{4+}$  by free holes in the VB at high potentials. That's to say, the difference of extinction coefficients should be the origin of the complicated trend in potential-dependent PIA amplitudes for CoPi/ $\text{Fe}_2\text{O}_3$ . Furthermore, the potential-dependent PIA spectra of CoPi/ $\text{Fe}_2\text{O}_3$ -air and CoPi/ $\text{Fe}_2\text{O}_3$ -Ar (Fig. S12<sup>†</sup>) with modified surface states display a similar change trend, suggesting that the potential-dependent PIA variation in electrocatalyst-coated  $\text{Fe}_2\text{O}_3$  can be related to the distribution of surface states, free holes in the VB and oxidation states of the electrocatalyst.

### Effect of stored holes in CoPi on charge transfer

After knowing the potentiodynamic hole storage mechanisms of loaded CoPi, the dissipation paths of holes in CoPi are further studied to uncover the function of CoPi in PEC water

oxidation. By comparing the potential-dependent PIA responses of bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  in Fig. 3a and c, the PIA spectra of the CoPi/ $\text{Fe}_2\text{O}_3$  photoanode display slower accumulation and dissipation processes. In order to specifically compare the kinetic change, the lifetimes of PIA accumulation and dissipation processes for bare  $\text{Fe}_2\text{O}_3$  and CoPi/ $\text{Fe}_2\text{O}_3$  photoanodes are fitted using a bi-exponential function in Fig. 3e and f (fitted results are shown in Table S1<sup>†</sup>). At 0.7–0.9  $V_{\text{RHE}}$ , drastic recombination leads to no accumulation processes in bare  $\text{Fe}_2\text{O}_3$ . After loading CoPi on the  $\text{Fe}_2\text{O}_3$  surface, the sequential hole transfer through surface states to oxidize  $\text{Co}^{2+}/\text{Co}^{3+}$  results in the long accumulation lifetimes of 2.4~3.8 s. With potential above 1.0  $V_{\text{RHE}}$ , the accumulation processes of the bare  $\text{Fe}_2\text{O}_3$  photoanode show an average lifetime of  $\sim 0.45$  s, which is faster than the shortest accumulation lifetime ( $\sim 0.62$  s) in the CoPi/ $\text{Fe}_2\text{O}_3$  photoanode. Due to concentrated electrolyte (1 M NaOH) and weak illumination ( $5 \text{ mW cm}^{-2}$ ) in PIA measurements, the slow accumulation lifetimes in the CoPi/ $\text{Fe}_2\text{O}_3$  photoanode shouldn't be due to the CoPi deposition caused by the local pH change under light irradiation.<sup>32</sup> Moreover, with the increase of applied potential, the first increasing then decreasing accumulation lifetimes in Fig. 3e also exclude diffusion-controlled CoPi deposition. Thus, this slow accumulation process is attributed to slow hole hopping from the CoPi/ $\text{Fe}_2\text{O}_3$  interface to the CoPi bulk after cobalt oxidation at the millisecond timescale. The prolonged accumulation lifetimes indicate that loaded CoPi induces new charge separation paths near the  $\text{Fe}_2\text{O}_3$  surface for promoting charge separation *via* cobalt oxidation by photoinduced holes. The smaller accumulation lifetimes with potential above 1.2  $V_{\text{RHE}}$  than that with potential below 1.0  $V_{\text{RHE}}$  suggest that the direct hole transfer to oxidize  $\text{Co}^{3+}/\text{Co}^{4+}$  is faster than the sequential hole transfer to oxidize  $\text{Co}^{2+}/\text{Co}^{3+}$ .



For dissipation processes, except the short lifetime ( $\sim 0.6$  s) near the onset potential, bare  $\text{Fe}_2\text{O}_3$  displays an almost constant dissipation lifetime about 1.2 s, in line with the understanding of the water oxidation reaction by free holes in the VB.<sup>3</sup> Namely, the increased potential for bare  $\text{Fe}_2\text{O}_3$  is used for suppressing recombination and increasing density of free holes in the VB, rather than changing the enthalpy or activation energy. In contrast, the dissipation lifetimes of  $\text{CoPi}/\text{Fe}_2\text{O}_3$  exhibit first an increased then decreased trend, resulting in the longest lifetime about 2.9 s at 1.0  $V_{\text{RHE}}$ . Due to the weak contribution to water oxidation of  $\text{CoPi}$  (Fig. 2c and d), the slow PIA decay should be attributed to the recombination process between stored holes in  $\text{CoPi}$  and photoinduced electrons on the  $\text{Fe}_2\text{O}_3$  surface. The dissipation lifetimes of 1.6  $\sim$  2.9 s (0.7–1.0  $V_{\text{RHE}}$ ) directly demonstrate the effective suppression of charge recombination by  $\text{Co}^{3+}$  states. When external potential increases to 1.6  $V_{\text{RHE}}$ , the dissipative average lifetime ( $\sim 1.6$  s) is still longer than the dissipation process of bare  $\text{Fe}_2\text{O}_3$  ( $\sim 1.2$  s), indicating that the oxidized  $\text{Co}^{4+}$  states also suppress the charge recombination effectively. The suppressed charge recombination is also supported by the TAS and TPC results (Fig. S7 and S11<sup>†</sup>).

Then, the charge recombination between oxidized  $\text{CoPi}$  and  $\text{Fe}_2\text{O}_3$  was investigated at high potential, to confirm the roles of oxidized  $\text{Co}^{4+}$  in PEC processes. In principle, if the  $\text{Co}^{4+}$  concentration is high enough in  $\text{CoPi}$  for the  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanode at the ground state, photogenerated hole transfer from  $\text{Fe}_2\text{O}_3$  to  $\text{CoPi}$  under illumination will be blocked. In consequence, more recombination events of photoinduced electrons and holes in  $\text{CoPi}$  will be observed, which will lead to decreased PIA amplitude. In order to confirm this hypothesis,  $\text{CoPi}$  was loaded on the porous  $\text{Fe}_2\text{O}_3$ . Since the conductive substrate (FTO) is partially bare, there exist triphasic interfaces of  $\text{FTO}/\text{CoPi}$ ,  $\text{FTO}/\text{Fe}_2\text{O}_3$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$ , as shown in Fig. S13a.<sup>†</sup> When potential is applied to  $\text{CoPi}/\text{porous-Fe}_2\text{O}_3$ ,  $\text{CoPi}$  can be directly oxidized to high-valent cobalt species ( $\text{Co}^{4+}$ ) resulting in typical redox waves (Fig. S13b<sup>†</sup>). Then the charge transfer processes of  $\text{CoPi}/\text{porous-Fe}_2\text{O}_3$  are studied using PIA.  $\text{CoPi}/\text{porous-Fe}_2\text{O}_3$  shows similar potential-dependent PIA spectra to that of the above dense  $\text{CoPi}/\text{Fe}_2\text{O}_3$  under low light intensity irradiation of  $5 \text{ mW cm}^{-2}$  (Fig. S14<sup>†</sup>). As expected, the PIA spectra in Fig. 4a display a negative amplitude at high potential (1.5  $V_{\text{RHE}}$ ) and under illumination ( $30 \text{ mW cm}^{-2}$ ). Additionally, the chopped photocurrent at 1.5  $V_{\text{RHE}}$  in Fig. 4b shows a disappearing transient spike, which can be understood by electron shunt transfer. Photoinduced electrons don't move from the porous  $\text{Fe}_2\text{O}_3$  surface to the bulk then to FTO, but from the porous  $\text{Fe}_2\text{O}_3$  surface to  $\text{CoPi}$  then to FTO resulting in a positive current. The oxidized  $\text{CoPi}$  can effectively capture photoinduced electrons, resulting in a flow of electrons at the moment of suddenly turning the light on/off. Because the flow of electrons induced by  $\text{CoPi}$  is opposite to the flow of back electrons, the disappearing transient spikes are observed. Thus, both PIA and photocurrent results of porous  $\text{Fe}_2\text{O}_3$  with loaded  $\text{CoPi}$  directly demonstrate the possibility of charge recombination between  $\text{Co}^{4+}$  species and photoinduced electrons of  $\text{Fe}_2\text{O}_3$ . Therefore, at high potential, loaded  $\text{CoPi}$  on dense/porous- $\text{Fe}_2\text{O}_3$  serves as a mediator to fast capture holes in

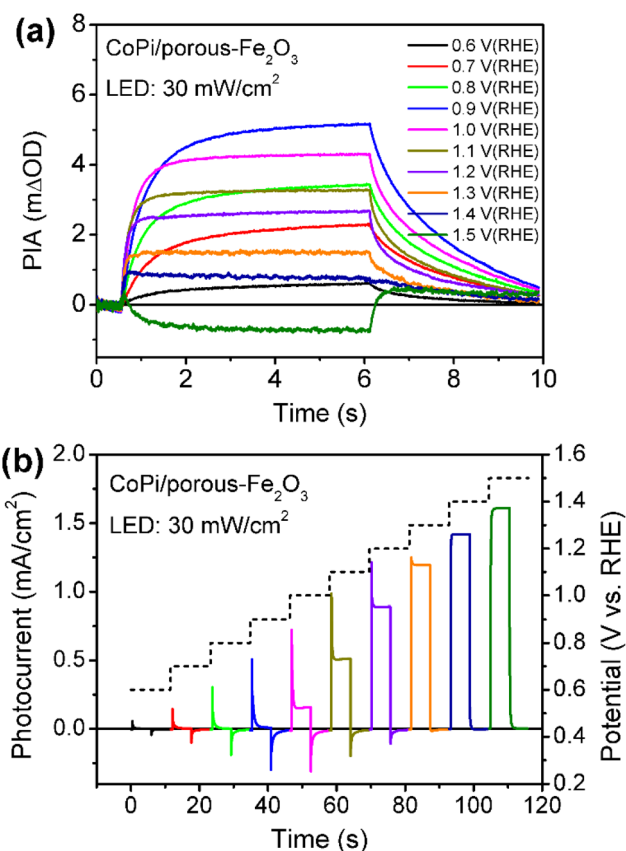


Fig. 4 Potential-dependent PIA spectra (a) and chopped photocurrents (b) for  $\text{CoPi}/\text{porous-Fe}_2\text{O}_3$ . Pump wavelength is 456 nm ( $30 \text{ mW cm}^{-2}$ ); probe wavelength is 694.3 nm; colors of curves at different potentials in (a and b) are identical.

the VB of  $\text{Fe}_2\text{O}_3$  followed by slow consumption by photogenerated electrons of the  $\text{Fe}_2\text{O}_3$  surface, which can slow down the recombination process and produce more long-lived holes for water oxidation.

To further understand the roles of electrocatalyst-mediated charge transfer processes in the PEC water oxidation reaction, we correlate reaction rate and hole density for  $\text{Fe}_2\text{O}_3$  without/without  $\text{CoPi}$  loading at increased potential. The light-intensity-dependent PIA spectra were recorded for bare  $\text{Fe}_2\text{O}_3$  and  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanodes. In Fig. 5a and b, PIA amplitudes for the two photoanodes increase with light intensity increasing at a fixed potential, suggesting more holes on the  $\text{Fe}_2\text{O}_3$  surface and promotional oxidation for  $\text{CoPi}$ . According to previous reports,<sup>4,12</sup> the photoinduced hole can directly be regarded as a reactant, and its reaction parameters can be quantified by rate analysis ( $r = J = k \times [h^+]^\beta$ , where  $r$  is the reaction rate and equivalent to current density ( $J$ ),  $k$  is the rate constant,  $[h^+]^\beta$  is the hole density and  $\beta$  is the reaction order). Due to the linear relation of PIA intensity and hole concentration in Fig. S15,<sup>†</sup> the reaction orders at changed potential from 0.6  $V_{\text{RHE}}$  to 1.6  $V_{\text{RHE}}$  are calculated and shown in Fig. 5c and d. Although PIA amplitudes of  $\text{Fe}_2\text{O}_3$  under fixed illumination display saturation above 1.2  $V_{\text{RHE}}$  due to surface states, there is an effective rate analysis at the fixed potential and changed illumination in



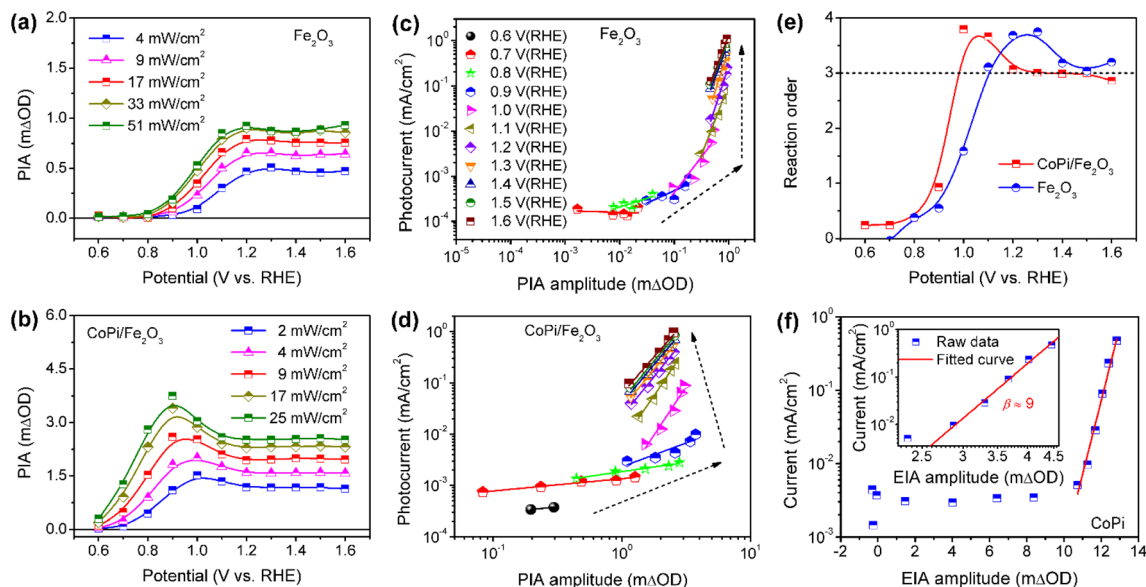


Fig. 5 Light-intensity-dependent PIA spectra of (a) bare  $\text{Fe}_2\text{O}_3$  and (b)  $\text{CoPi}/\text{Fe}_2\text{O}_3$  at increased potential. Pump wavelength is 456 nm; probe wavelength is 694.3 nm. Rate law analysis for (c)  $\text{Fe}_2\text{O}_3$  and (d)  $\text{CoPi}/\text{Fe}_2\text{O}_3$ . The colors of lines at various potentials in (c and d) are identical. (e) Reaction order of the two photoanodes as a function of potential. (f) Log(current) versus hole density from EIA spectra for the CoPi electrocatalyst. The inset shows the rate law analysis with corrected hole density for the CoPi electrocatalyst.

Fig. 5a. This result demonstrates that there is a linear scaling relationship of photoinduced hole density distribution between the VB and surface states in the present study. With potential increase, the reaction order of  $\text{Fe}_2\text{O}_3$  displays first an increase to a maximum value (from zero to fourth) and then a decrease to a constant (from fourth to third) value in Fig. 5e, implying that surface states participate in or modulate the surface reaction. After loading CoPi on the  $\text{Fe}_2\text{O}_3$  surface, in line with the scaling relationship of hole density with PIA (Fig. S15d†), a similar linear shape for the reaction order–potential relation is obtained. Particularly, the maximum (fourth) and constant (third) reaction orders for  $\text{CoPi}/\text{Fe}_2\text{O}_3$  arise at lower potential than bare  $\text{Fe}_2\text{O}_3$  (Fig. 5e), illustrating similar functions of surface states and coated CoPi electrocatalyst. Furthermore, Fig. 5f demonstrates that the relationship of hole density (electro-induced absorption (EIA) intensity) and current in the CoPi electrocatalyst obeys an Eyring-like equation ( $\log(j) \propto [h^+]$ ) reported by Hong Nhan Nong,<sup>33</sup> rather than rate analysis that shows a high-order reaction ( $\beta \approx 9$ ) for electrocatalytic current from microampere to milliamper. These results demonstrate that surface states and the loaded electrocatalyst can directly receive and store a part of holes from the VB of hematite, but don't affect the reaction kinetics of reaction sites.


## Discussion

The charge transfer processes for three kinds of hole storage sites at the interface of  $\text{Fe}_2\text{O}_3$ , CoPi and water under illumination and at applied potential are summarized in Scheme 1. As discussed above, there are surface states for bare  $\text{Fe}_2\text{O}_3$  with a potential distribution in the 0.8–1.4  $V_{\text{RHE}}$  range.

These surface states are occupied by intrinsic electrons, which can only be removed by illumination (trapping holes). Due to limited oxidation activity, the surface states play a role in aggravating recombination of photoinduced charges resulting in large onset potential of bare  $\text{Fe}_2\text{O}_3$ . Moreover, the holes of surface states at low potential ( $\leq 0.8 V_{\text{RHE}}$ ) can only oxidize  $\text{Co}^{2+}$  to  $\text{Co}^{3+}$  rather than  $\text{Co}^{3+}$  to  $\text{Co}^{4+}$  and water oxidation, which is the main charge transfer path in the  $\text{CoPi}/\text{Fe}_2\text{O}_3$  photoanode (the left panel of Scheme 1). This process is a sequential hole transfer from the VB to surface states (ps ~ ns)<sup>34</sup> then to CoPi (~0.6 s), followed by recombination with photoinduced electrons ( $\geq 1.3$  s) resulting in dissipation of hole energy. Slower recombination in  $\text{CoPi}/\text{Fe}_2\text{O}_3$  is the origin of the negative shift of onset potential.

At high potential ( $\geq 1.4 V_{\text{RHE}}$ ), the space charge region and band-bending of  $\text{Fe}_2\text{O}_3$  will be broadened and increased, respectively (the right panel of Scheme 1). Under quasi-steady-state illumination and at high potential, photoinduced holes can completely fill the surface states and oxidize  $\text{Co}^{2+}$  to  $\text{Co}^{3+}$  via the sequential hole transfer process. Although surface states on the bare  $\text{Fe}_2\text{O}_3$  surface can be completely occupied by trapping holes, the photocurrent is still lower than the theoretical value due to inevitable recombination loss by back electrons (Fig. S11†). Because of the delayed recombination process at high potential, more high-energy and long-lived holes in the VB will be generated to directly contribute to water oxidation (OER: ~0.2 s), as well as  $\text{Co}^{3+}$  oxidation ( $\text{Co}^{3+/4+}$ : ~0.8 s). Nevertheless, although CoPi acts as the hole storage site, CoPi still doesn't contribute to PEC water oxidation due to low  $\text{Co}^{4+}$  density. However, the stored holes in CoPi are not static spectators but dynamic charge mediators, which can again capture photoinduced electrons for a long time. Owing to spatial charge



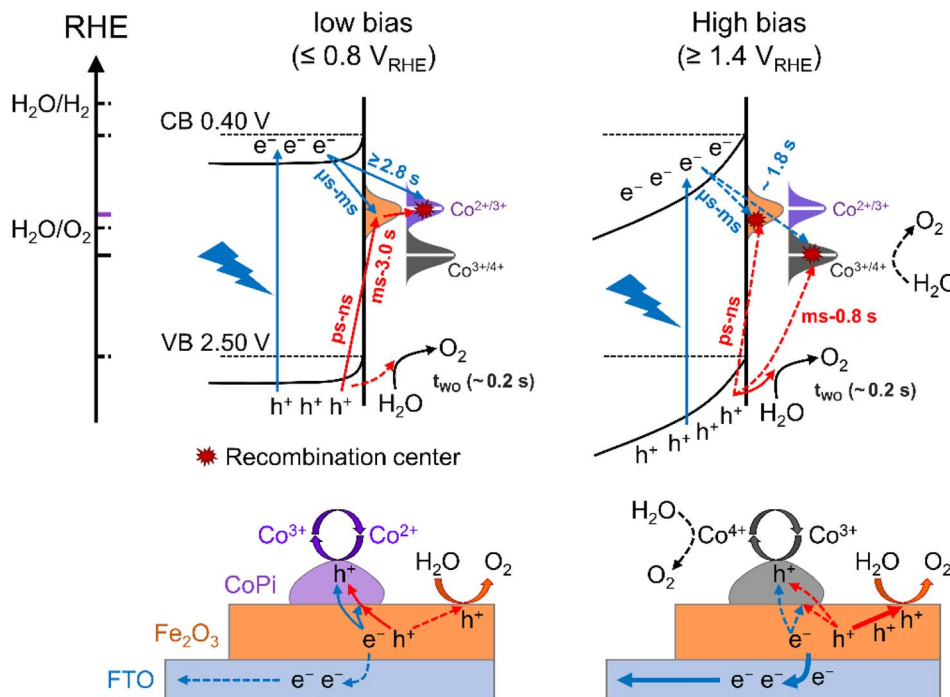

**Scheme 1** Kinetic schematic of photoinduced charge transfer at the interface of  $\text{Fe}_2\text{O}_3$  and CoPi under illumination and at applied potential from energy (top panel) and space (bottom panel) scenarios. The potential distribution of surface states (orange),  $\text{Co}^{2+/3+}$  (purple) and  $\text{Co}^{3+/4+}$  (grey) are displayed as Gaussian curves. Colored (solid) lines “—” are representative of redox potentials of cobalt species, hydrogen generation and oxygen generation. Red and blue arrows refer to transfer processes of photogenerated electrons and photoinduced holes, respectively (the dashed and solid lines indicate the transferred amount of photoinduced charges).

separation of photogenerated electrons ( $\text{Fe}_2\text{O}_3$  surface) and trapped holes (CoPi electrocatalyst), CoPi/ $\text{Fe}_2\text{O}_3$  displays longer recombination lifetimes resulting in enhanced PEC performances.

As shown by the spectroscopic results, the delayed recombination between photogenerated electrons of  $\text{Fe}_2\text{O}_3$  and trapped holes of CoPi electrocatalyst due to spatial charge separation will improve PEC performances of CoPi/ $\text{Fe}_2\text{O}_3$ , which can be applied to all potentials with photo-response. There are connections and differences between this new viewpoint and previous reports. Although surface state passivation to decrease recombination is common understanding,<sup>26,35,36</sup> the EIS results in Fig. 1d reveal that loaded CoPi leads to more surface states, demonstrating negligible contribution of surface state passivation. Using TAS and PIA, Durrant found consistent spectral shapes and long-lived holes after loading CoPi on the  $\text{Fe}_2\text{O}_3$  surface, which are attributed to enhanced electron depletion by broadening the space charge region.<sup>14,22,24,25</sup> Besides reproducing the reported results, our potential- and light-intensity-dependent spectra further reveal that loaded CoPi on the  $\text{Fe}_2\text{O}_3$  surface displays potentiodynamic hole storage mechanisms and acts as a hole storage site of delayed recombination. On the other hand, although Boettcher claimed the direct catalysis evidence of CoPi by tracking surface potential of loaded CoPi in PEC water oxidation,<sup>18</sup> the microscopic measurement of AFM might not reflect the overall character of loaded CoPi electrocatalyst. Nevertheless, because of the ensemble-averaged measurements in spectroscopy,

present experiments can't completely exclude that a loaded electrocatalyst (like CoPi) on the  $\text{Fe}_2\text{O}_3$  surface has no contribution to water oxidation. Instead, we are convinced that a large proportion of the electrocatalyst only acts as a mediator that stores photoinduced holes and recombines with photo-generated electrons. Considering the key role of photo-generated electrons in PEC performance of  $\text{Fe}_2\text{O}_3$ , several strategies of influencing photogenerated electrons on/near the surface were employed, which display considerable PIA difference (Fig. S16<sup>†</sup>), such as decreasing density of electron trap states by surface covalent doping with fluorine (Fig. S16a<sup>†</sup>),<sup>37</sup> reducing reverse recombination of electrons *via* surface insulator modification ( $\text{SnO}_2$ ) (Fig. S16b<sup>†</sup>)<sup>38</sup> and enhancing separation efficiency of photoinduced charges by constructing a built-in electric field using a homojunction (Fig. S16c<sup>†</sup>).<sup>15</sup> These results demonstrate that controlling recombination of photogenerated electrons plays a remarkable role in charge dynamics, highlighting the importance of regulating charge transfer processes at the semiconductor–electrolyte interface.

## Conclusions

We studied the charge transfer mechanisms among surface states, reaction sites and the coated electrocatalyst in  $\text{Fe}_2\text{O}_3$  without/with CoPi by PIA spectroscopy. Surface states in  $\text{Fe}_2\text{O}_3$  are not removed by loading CoPi, but serve as a mediator. At low potential, photoinduced holes of the VB are preferentially trapped into surface states and trapped holes further move to





CoPi, presenting a sequential hole transfer. Photoinduced holes at high potential are prone to direct water oxidation by holes of the VB on the Fe<sub>2</sub>O<sub>3</sub> surface, resulting in constant and decreasing PIA signals for Fe<sub>2</sub>O<sub>3</sub> and CoPi/Fe<sub>2</sub>O<sub>3</sub> photoanodes, respectively. Namely, there appears a dynamic transition in collecting holes for CoPi from surface states to the VB with increasing potential. More importantly, loaded CoPi did not serve as a catalyst to change third-order water oxidation reaction kinetics on the Fe<sub>2</sub>O<sub>3</sub> surface, but promotes spatial separation of photoinduced charges resulting in long-lived holes for facilitating PEC water oxidation performance. The dynamic charge collecting mechanism not only deepens the understanding of the roles of the loaded electrocatalyst in PEC, but also helps the designing of the microstructure of electrocatalyst loaded photoanodes.

## Data availability

All experimental and characterization data are available in the ESI.†

## Author contributions

D. L., X. W. and C. L. conceived the research. D. L. carried out the experiments, analyzed data and wrote the manuscript. R. W. and H. Y. analyzed data. H. Z. provided the homojunction sample. X. W. and C. L. discussed the data and revised the manuscript. All authors have given approval to the final version of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We acknowledge financial support from the National Key R&D Program of China (2021YFA1500600), the National Natural Science Foundation of China (21872143), the Fundamental Research Center of Artificial Photosynthesis (FReCAP), and the DICP Foundation of Innovative Research (DICP I202122).

## Notes and references

- I. Roger, M. A. Shipman and M. D. Symes, *Nat. Rev. Chem.*, 2017, **1**, 1–13.
- C. Ding, J. Shi, Z. Wang and C. Li, *ACS Catal.*, 2016, **7**, 675–688.
- S. Corby, R. R. Rao, L. Steier and J. R. Durrant, *Nat. Rev. Mater.*, 2021, **6**, 1136–1155.
- C. A. Mesa, L. Francàs, K. R. Yang, P. Garrido-Barros, E. Pastor, Y. Ma, A. Kafizas, T. E. Rosser, M. T. Mayer, E. Reisner, M. Grätzel, V. S. Batista and J. R. Durrant, *Nat. Chem.*, 2020, **12**, 82–89.
- C. Li, Z. Luo, T. Wang and J. Gong, *Adv. Mater.*, 2018, **30**, 1707502.
- D. R. Gamelin, *Nat. Chem.*, 2012, **4**, 965–967.
- D. A. Grave, N. Yatom, D. S. Ellis, M. C. Toroker and A. Rothschild, *Adv. Mater.*, 2018, **30**, 1706577.
- D. Zhou and K. Fan, *Chin. J. Catal.*, 2021, **42**, 904–919.
- O. Zandi and T. W. Hamann, *Nat. Chem.*, 2016, **8**, 778–783.
- Y. Zhang, H. Zhang, A. Liu, C. Chen, W. Song and J. Zhao, *J. Am. Chem. Soc.*, 2018, **140**, 3264–3269.
- B. Klahr and T. Hamann, *J. Phys. Chem. C*, 2014, **118**, 10393–10399.
- F. Le Formal, E. Pastor, S. D. Tilley, C. A. Mesa, S. R. Pendlebury, M. Gratzel and J. R. Durrant, *J. Am. Chem. Soc.*, 2015, **137**, 6629–6637.
- B. Klahr, S. Gimenez, F. Fabregat-Santiago, T. Hamann and J. Bisquert, *J. Am. Chem. Soc.*, 2012, **134**, 4294–4302.
- M. Barroso, C. A. Mesa, S. R. Pendlebury, A. J. Cowan, T. Hisatomi, K. Sivula, M. Gratzel, D. R. Klug and J. R. Durrant, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 15640–15645.
- H. Zhang, D. Li, W. J. Byun, X. Wang, T. J. Shin, H. Y. Jeong, H. Han, C. Li and J. S. Lee, *Nat. Commun.*, 2020, **11**, 4622.
- J. Qiu, H. Hajibabaei, M. R. Nellist, F. A. L. Laskowski, S. Z. Oener, T. W. Hamann and S. W. Boettcher, *ACS Energy Lett.*, 2018, **3**, 961–969.
- P. Shadabipour and T. W. Hamann, *Chem. Commun.*, 2020, **56**, 2570–2573.
- M. R. Nellist, F. A. L. Laskowski, J. Qiu, H. Hajibabaei, K. Sivula, T. W. Hamann and S. W. Boettcher, *Nat. Energy*, 2017, **3**, 46–52.
- M. R. Nellist, J. Qiu, F. A. L. Laskowski, F. M. Toma and S. W. Boettcher, *ACS Energy Lett.*, 2018, **3**, 2286–2291.
- G. M. Carroll, D. K. Zhong and D. R. Gamelin, *Energy Environ. Sci.*, 2015, **8**, 577–584.
- J. Xiao, L. Fan, Z. Huang, J. Zhong, F. Zhao, K. Xu, S.-F. Zhou and G. Zhan, *Chin. J. Catal.*, 2020, **41**, 1761–1771.
- Y. Ma, A. Kafizas, S. R. Pendlebury, F. Le Formal and J. R. Durrant, *Adv. Funct. Mater.*, 2016, **26**, 4951–4960.
- J. Li, W. Wan, C. A. Triana, Z. Novotny, J. Osterwalder, R. Erni and G. R. Patzke, *J. Am. Chem. Soc.*, 2019, **141**, 12839–12848.
- M. Barroso, A. J. Cowan, S. R. Pendlebury, M. Gratzel, D. R. Klug and J. R. Durrant, *J. Am. Chem. Soc.*, 2011, **133**, 14868–14871.
- Y. Ma, F. Le Formal, A. Kafizas, S. R. Pendlebury and J. R. Durrant, *J. Mater. Chem. A*, 2015, **3**, 20649–20657.
- C. Zachus, F. F. Abdi, L. M. Peter and R. van de Krol, *Chem. Sci.*, 2017, **8**, 3712–3719.
- Z. Wang, G. Liu, C. Ding, Z. Chen, F. Zhang, J. Shi and C. Li, *J. Phys. Chem. C*, 2015, **119**, 19607–19612.
- B. Klahr, S. Gimenez, F. Fabregat-Santiago, J. Bisquert and T. W. Hamann, *J. Am. Chem. Soc.*, 2012, **134**, 16693–16700.
- C. A. Mesa, L. Steier, B. Moss, L. Francas, J. E. Thorne, M. Gratzel and J. R. Durrant, *J. Phys. Chem. Lett.*, 2020, **11**, 7285–7290.
- J. Yuan, Y. Yuan, J. Zhang, H. Xu, Z. Mao and Y. Ma, *ChemSusChem*, 2022, **15**, e202102313.
- S. R. Pendlebury, A. J. Cowan, M. Barroso, K. Sivula, J. Ye, M. Grätzel, D. R. Klug, J. Tang and J. R. Durrant, *Energy Environ. Sci.*, 2012, **5**, 6304–6312.



- 32 Y. Surendranath, D. A. Lutterman, Y. Liu and D. G. Nocera, *J. Am. Chem. Soc.*, 2012, **134**(14), 6326–6336.
- 33 H. N. Nong, L. J. Falling, A. Bergmann, M. Klingenhof, H. P. Tran, C. Spöri, R. Mom, J. Timoshenko, G. Zichittella, A. Knop-Gericke, S. Piccinin, J. Pérez-Ramírez, B. R. Cuenya, R. Schlögl, P. Strasser, D. Teschner and T. E. Jones, *Nature*, 2020, **587**, 408–413.
- 34 M. Barroso, S. R. Pendlebury, A. J. Cowan and J. R. Durrant, *Chem. Sci.*, 2013, **4**, 2724.
- 35 J. E. Thorne, J.-W. Jang, E. Y. Liu and D. Wang, *Chem. Sci.*, 2016, **7**, 3347–3354.
- 36 J. Lee, D. Seo, S. Won and T. D. Chung, *Sustainable Energy Fuels*, 2021, **5**, 501–508.
- 37 S. Chen, J. Bai, X. Nurimaimaiti, J. Wang, Y. Zhang, T. Zhou, J. Li and B. Zhou, *Nano Energy*, 2020, **78**, 105396.
- 38 T. Hisatomi, H. Dotan, M. Stefik, K. Sivula, A. Rothschild, M. Gratzel and N. Mathews, *Adv. Mater.*, 2012, **24**, 2699–2702.

