



Cite this: *Catal. Sci. Technol.*, 2024, **14**, 1712

Recent advances in promoting dry reforming of methane using nickel-based catalysts

Haibin Zhu, Huichao Chen,* Menghan Zhang, Cai Liang and Lunbo Duan

Dry reforming of methane (DRM) is an efficient way for CO₂ utilization to convert CH₄ and CO₂ to syngas (H₂ and CO), which is an ingredient to produce hydrogen and methanol and hydrocarbons via Fischer-Tropsch process. Considerable attention is drawn to Ni-based catalyst due to its remarkable reactivity for CH₄ and CO₂ conversion. However, the weakness of sintering and coking restrains its industrial applications. The successful design of cost-effective, efficient and stable Ni-based catalysts would be a grand breakthrough for the technology. Herein, the thermodynamic analysis and the mechanisms of sintering and coking are presented. Then, the strategies for improving the performance of catalysts are elaborated as follows, with 1) supports improving the particle dispersion of nickels and changing the reaction process for the hindrance of coking; 2) promoters for regulating the nickel's chemical properties to enable catalytic DRM performance; 3) catalysts obtained by varied preparation methods possess different sizes and interactions. Finally, the challenges and future perspectives are highlighted.

Received 21st November 2023,
Accepted 9th February 2024

DOI: 10.1039/d3cy01612a

rsc.li/catalysis

Introduction

The fast growth of human society has significantly increased fossil fuel consumption, and the excessive carbon dioxide (CO₂) emission, which has passed 41 billion tons per year, has led to a variety of issues, the most prominent of which is the growing greenhouse effect.^{1–4} In this context, methane (CH₄) is more active than CO₂ in the greenhouse effect.^{5,6} Conceptually, inserting CO₂ as a reactant into the process of fuel or chemical production could provide tangible negative emissions.^{7,8} Dry

reforming of methane (DRM) is a promising way of CO₂ utilization with the production of syngas (H₂ and CO) and has been studied since 1885.^{5,9–11} DRM attracts interests of researchers because of the advantages of simultaneously eliminating both CO₂ and CH₄. The origin of the gas may be industrial emissions or biogas, predominantly consisting of methane and CO₂, substances that are abundantly generated in present-day industrial process or through the anaerobic digestion or fermentation of organic matter by microbes.^{12,13}

DRM provides a feasible way for Carbon Capture, Utilization & Storage (CCUS). Taking hydrogen production as an example, currently, its global scale is more than 60 Mt per year from the process of steam reforming (CH₄ + H₂O → CO + 3H₂, $\Delta H_{298K}^0 = 206 \text{ kJ mol}^{-1}$).^{1,14} If this process is replaced by DRM (CH₄ + CO₂

School of Energy and Environment, Southeast University, Nanjing 210096, China.
E-mail: hcchen@seu.edu.cn



Haibin Zhu

Haibin Zhu is a postgraduate student in the School of Energy and Environment, Southeast University, China. His current research focuses on the development of novel catalysts for carbon capture and conversion into value-added products.



Huichao Chen

Huichao Chen is Associate Professor at the School of Energy and Environment at Southeast University, China. Her research interests include carbon dioxide capture and utilization and contaminated soil remediation.



→ CO + 2H₂, $\Delta H_{298K}^0 = 247$ kJ mol⁻¹), nearly 30 Mt per year of CO₂ emissions could be removed, providing a large anthropogenic carbon sink to only 0.25 Gt per year in the current CO₂ market.^{1,14,15} Meanwhile, DRM can also produce syngas, and these syngas components can be further processed into hydrocarbons, enabling the production of environmentally friendly fuels and valuable high-value chemicals (Fig. 1).¹⁶⁻¹⁸ Considering the carbon peaking and carbon neutrality proposed by the Chinese government, DRM offers a promising solution for addressing the surplus CO₂ emissions while maintaining the integrity of existing infrastructure.¹⁹ Nevertheless, challenges such as the sintering of nickel metal particles and carbon deposition on the catalysts hinder its widespread commercial application.²⁰

To implement DRM in wide industrial application, it is significant to develop cost-efficient, highly active and exceptionally stable catalysts.²² Among the metal catalysts, nickel (Ni)-based catalysts are more practical because of its cost-efficiency and comparable catalytical performance over other noble metals (Ru-based and Rh-based catalysts).²³⁻²⁵ However, high temperature is required for the reaction as CO₂ is thermodynamically stable and for the suppression of side

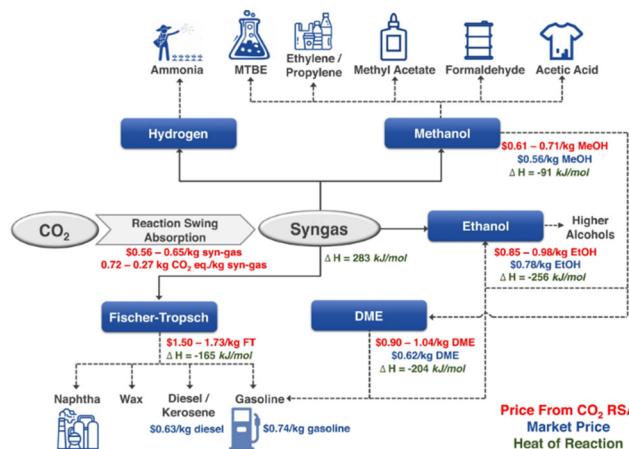


Fig. 1 Syngas as a versatile intermediate chemical (RSA presents reaction swing absorption). Reproduced from ref. 21 with permission from Nature Communications, copyright 2022.

effects as well. Thus, the catalysts suffer from sintering and rapid carbon deposition caused by high reaction temperature, which hinders its implementation at the industrial scale.

Rapid development of technology has been made and it is necessary to review the advances and challenges for further promoting the technology for wide application. Therefore, the present review focuses on the thermodynamics, reaction mechanism, and the efforts for improving the catalytic activity and stability from the aspects of supports, promoters, and synthesis methods. Furthermore, the challenges and opportunities associated with the nickel-based catalysts in DRM are proposed in the end.



Menghan Zhang is a PhD student at the School of Energy and Environment, Southeast University, China. Her research interests include the development of calcium-based sorbents for CO₂ capture.

Menghan Zhang



Cai Liang is Professor at the School of Energy and Environment at Southeast University, China. His main research interests focus on clean coal technology and hydrogen from waste plastics.

Cai Liang

Thermodynamics, reaction mechanism, sintering and carbon deposition

Thermodynamics

Fig. 2 illustrates the thermodynamic analysis of the reactions taking place under the conditions of DRM in



Lunbo Duan is Professor at the School of Energy and Environment at Southeast University, China. Prof. Duan is also the vice chairman of Jiangsu Power Engineering Society. His main research interests focus on CO₂ emission reduction and advanced energy materials.

Lunbo Duan



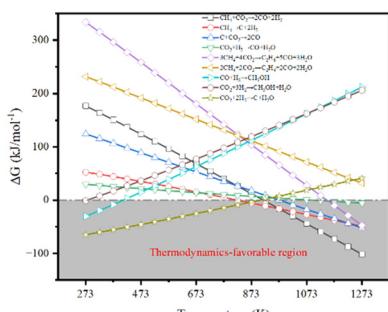


Fig. 2 The thermodynamics of main reactions under the conditions of DRM.

terms of Gibbs free-energy changes (ΔG_T^θ) obtained by the Outokumpu HSC Chemistry® program. Although the DRM reaction is mainly dominated by methane dissociation (or methane dehydrogenation, eqn (2)²⁶ in Table 1) and reverse Boudouard reaction (or CO_2 activation, eqn (3)²⁶), some side reactions occur at the same time (eqn (5)–(9)).^{27–30} To obtain high conversion of CH_4 and CO_2 and selectivity toward syngas, the DRM temperature should be mostly above 873 K, which is not favorable for the side reactions and methane dissociation,²⁸ reverse Boudouard reaction and reverse water-gas shift reaction (RWGS, eqn (4)²⁸). Furthermore, the reverse Boudouard reaction and RWGS reaction are responsible for the carbon deposition because of the faster rate of methane dissociation over the reverse Boudouard reaction gap of ΔG_T^θ .^{31,32} The formed carbonaceous species would remain on the active sites surface and hinder the access of CO_2 and CH_4 to the inner unreacted active sites.^{33,34} CO_2 is also likely to react with H_2 from the methane dissociation, according to the RWGS (eqn (4)), leading to a H_2/CO ratio less than 1.0,^{35,36} related to the equilibrium at temperature ranges.^{29,35,37} To minimize the effect, high temperature for reaction and timely products removal is required.

Reaction mechanism

There is a consensus that the methane dihydrogen on the catalysts constitutes the step that dictates the reaction rate,¹ and this process follows the rules (Fig. 3): $^*\text{CH}_4 \rightarrow ^*\text{CH}_3 + ^*\text{H}$ (‘*’ refers Ni-based

active sites) and the formed $^*\text{H}$ combines consequently to form H_2 .^{38–41} Each partially dissociated $^*\text{CH}_x$ (“x” refers to 2, 3, 4) species adsorbs on Ni-based active sites, which completes its tetravalency.²⁹ Then, the CO_2 in stream reacts with $^*\text{C}$ to form CO according to the reverse Boudouard reaction, where CO_2 decomposes to the surface oxygen ($^*\text{O}$) and CO .⁴² During the process of reverse Boudouard reaction, $^*\text{O}$ reacts with $^*\text{CH}_x$ or produces intermediates of $^*\text{CH}_x\text{O}$ and $^*\text{CO}$ ($^*\text{CH}_x\text{O}$ is considered as the precursors of $^*\text{CO}$). In contrast, others hold the view that CO_2 forms carbonates firstly and the carbonates are subsequently reduced by $^*\text{C}$ from methane dissociation. Thus, whether CO_2 dissociates to $^*\text{O}$ and $^*\text{CO}$ or it forms carbonates first remains controversial. In general, challenges remain due to the absence of a well-established consensus regarding the intricacies of the reaction mechanism occurring on the catalytic surfaces.^{29,43,44}

Sintering

When the Ni-based catalysts are employed in the DRM, especially at a high temperature, there is a strong propensity for sintering, which results in the acceleration of particles growth due to the sharply increased surface energy with decreased nickel size. Sintering inevitably leads to the loss of surface area and deactivates the catalytic activity of the catalysts.⁴⁶ A fundamental understanding of Ni-based catalyst sintering is essential for the development of thermally stable catalysts.⁴⁷

Particles moving across the particle diffusion distance to contact with each other is the basic mechanism of sintering. Thus, increasing the particle distance on supports by using porous or mesoporous materials^{48,49} to achieve uniform spatial distribution⁵⁰ could slow down the sintering. Different preparation methods are used for developing unique structures (*i.e.*, core–shell structure^{51,52}), and supports are selected for regulating the nickel metal–support interactions.⁵³ Despite the promising approaches, diminishing the specific surface areas and increasing the resistance over mass-transfer results in decreasing conversions of CO_2 and CH_4 . Besides, the intricate geometric modification strategies of catalysts often involve complex multi-step procedures, making them difficult to implement on the industrial scale. At the same time, there is still limited understanding regarding the quantification of the

Table 1 The main reactions in the DRM process

Equation	Reaction	Reaction equation	$\Delta H_{298\text{K}}^\theta$ (kJ mol ⁻¹)
1	Main reaction	$\text{CH}_4 + \text{CO}_2 \rightarrow 2\text{CO} + 2\text{H}_2$	+247.016
2	Methane dissociation	$\text{CH}_4 \rightarrow 2\text{H}_2 + \text{C}$	+74.595
3	Reverse Boudouard reaction	$\text{CO}_2 + \text{C} \rightarrow 2\text{CO}$	+174.472
4	Reverse water-gas shift reaction	$\text{CO}_2 + \text{H}_2 \rightarrow \text{CO} + \text{H}_2\text{O}$	+41.138
5	Other side reactions	$3\text{CH}_4 + 4\text{CO}_2 \rightarrow \text{C}_2\text{H}_6 + 5\text{CO} + 3\text{H}_2\text{O}$	+434.946
6		$2\text{CH}_4 + 2\text{CO}_2 \rightarrow \text{C}_2\text{H}_4 + 2\text{CO} + 2\text{H}_2\text{O}$	+283.872
7		$\text{CO} + 2\text{H}_2 \rightarrow \text{CH}_3\text{OH}$	-90.452
8		$\text{CO}_2 + 3\text{H}_2 \rightarrow \text{CH}_3\text{OH} + \text{H}_2\text{O}$	-49.314
9		$\text{CO}_2 + \text{H}_2 \rightarrow \text{C} + \text{H}_2\text{O}$	-90.144



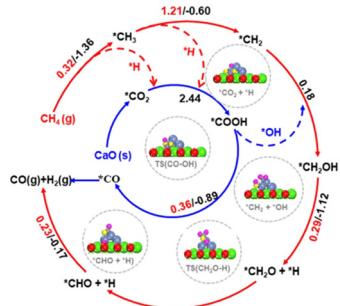


Fig. 3 Schematic diagram of methane dry reforming reaction. The corresponding activation energy is E_a (red) and reaction energy (black) is in the unit of eV for each step. Reproduced from ref. 45 with permission from Nature Communications, copyright 2023.

particles distance where a significant suppression of metal sintering occurs. Such fundamental knowledge is vital for developing sintering-resistant Ni-based catalysts for sustainable and economical catalytic processes.

The metal sintering mechanisms can be categorized into two types by their microscopic migration properties: (1) particle migration and coalescence (PMC), where nickel particles migrate under Brownian motion, resulting in collisions that consequently cause coalescence when two particles are close; (2) Ostwald ripening (OR), where the migration of nickel particles is propelled by a decrease in the chemical potential, with the particles released from an individual particle, dispersing across the support and adhering to adjacent ones, and culminating in the formation of larger particles (Fig. 4).^{46,54}

Carbon deposition

Sintering tends to expedite carbon deposition, supported by substantial evidence indicating a proclivity for coke formation on the surfaces of larger nickel particles.⁵⁶⁻⁵⁹ As coke is deposited, catalysts would become immobilized due to blockage. The carbonaceous deposits can be chemically adsorbed in the form of a strongly bonded monolayer or

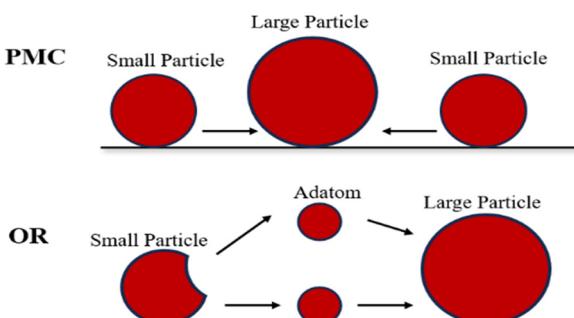


Fig. 4 Schematic diagram of sintering process. Reproduced from ref. 55 with permission from Accounts of Chemical Research, copyright 2013.

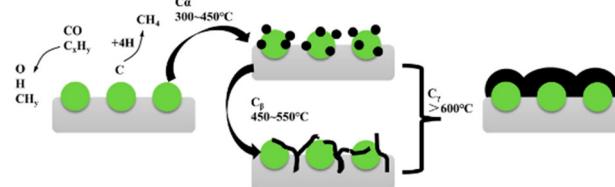


Fig. 5 Schematic diagram of carbon formation and transformation. Reproduced from ref. 33 with permission from *Atmosphere*, copyright 2023.

physically adsorbed as multiple layers, leading to the complete encasement of the metal active sites or obstructing pores. This significantly impedes the access of reactive substances to the nickel active sites.⁶⁰

The process of carbon deposition and transformation is shown in Fig. 5. According to the energy of carbonaceous species, three carbonaceous species can be distinguished:^{61,62} (I) adsorbed atomic carbon (C_α): C_α is a combination of *CH_x fragments from CH_4 and CO_2 on the catalytic surface.⁶³ It is the highly active atom that can mostly react with CO_2 or be further gasified;²² (II) filamentous carbon (C_β): C_β is a type of low-activity carbon species and originates from the C_α that reacts with water, carbon dioxide and hydrogen. It would be further gasified or encapsulated into nickel microcrystals, poisoning the catalysts; (III) graphite carbon (C_γ): C_γ is transformed by C_β at high temperature (>873 K). Among the carbonaceous species (C_α , C_β , and C_γ), C_β and C_γ are worthy of special attention since they are difficult to be oxidized and would destroy the catalyst structure.^{13,64-66}

As mentioned above, catalytic sintering and inactive carbon deposition easily deactivate the catalytic performance of the catalysts. Thermodynamic analysis has shown that the DRM occurs better at a high temperature of 873 K for reactant conversion and product selectivity, turning the ratio of CH_4 and CO_2 to unity.⁶⁷ However, the severe temperature would lead to high consumption of energy, which is not sustainable or economic. Meanwhile, the Ni particles inevitably aggregated under severe conditions, leading to the enhancement of carbon deposition and activity reduction. Therefore, more and more researchers have researched the modification of the catalysts to maintain the DRM stability and performance at a relatively low temperature according to Le Chatelier's principle. Many strategies have been proposed, such as choosing different supports to protect the active atoms migrating by the confinement effect, regulating the features of acidity and alkalinity, adding various promoters to change the Ni valence state or switching to other reaction paths to avoid carbon formation. Novel preparation methods are implemented to obtain catalysts with different interactions between metal and supports and structures like core-shell, perovskite, and hydrotalcite. A comprehensive review of the recent advances with respect to the dry reforming of methane, especially the modification and preparation of active catalysts, is summarized.

Influencing factors on the catalytic performance of Ni-based catalysts

Support selectivity

Because of the small specific surface area and few active sites of Ni particles, normally, they are not used independently.⁶⁸ The combination of Ni and supports possessing large surface area facilitates areas for nickel metal dispersion and diminishes the rate of carbon deposition.⁶⁹ Commonly employed support materials consist of alumina oxide, various types of clay, zeolites and structured mesoporous silicates featuring ordered pore structures.^{69–71} The supports not only physically hold the Ni nanoparticles by the confinement effect caused by their uneven surface but also influence the catalytic activity and coking resistance due to their surface acid–base feature.⁷² Meanwhile, the strong interaction between Ni nanoparticles and supports reduces the size, enhancing the dispersion of active sites.⁷³ Due to the high reaction temperature of DRM (usually above 700 °C), the suitable supports must have strong stability at high temperature and large specific surface area inhibiting the particles aggregation.⁷⁴ Table 2 summarizes the reaction conditions and CH₄ and CO₂ conversions by different support species.

Among the various supports, Al₂O₃ and SiO₂ are the most widely investigated. Researchers have synthesized numerous well-dispersed Ni/Al₂O₃ and Ni/SiO₂ *via* various preparation precursors and synthesis methods to increase the surface area, such as direct hydrogen calcination in the calcination process,⁷⁵ solvothermal method,⁷⁶ and sequential treatment method.^{78,84} The coke deposition level of these prepared catalysts is reduced relative to the Ni/Al₂O₃ synthesized by the typical co-precipitation method of a random morphology, and the coke tolerance is greatly improved relative to the precipitation catalyst, which has small and randomly distributed pores. The different crystalline phases suggest that α -Al₂O₃ is a hexagonal close-packed crystal and γ -Al₂O₃ is a cubic compact crystal, making Al₂O₃ present various characteristics.⁸⁵ The Ni/ γ -Al₂O₃ not only had a large BET surface area and pore volume, facilitating the Ni dispersion on the catalysts and enhancing its anti-coking ability, but maintained high CH₄ and CO₂ conversions, indicating no decrease in the DRM activity even with the availability of the deposited carbon on the catalysts.^{77,86}

However, there remain two contemporary challenges facing Ni-based catalysts with mesoporous Al₂O₃ and SiO₂ as supports.⁸⁷ Firstly, 1-dimensional nanotubes SiO₂ possess small pores with low specific surface and provide an easy

Table 2 Performance of Ni-based catalysts with different supports for DRM reactions

Catalyst	Temp (°C)	Time (h)	GHSV ^a and feed gas ratio	Conversion (%)	Carbon deposition
Ni/Al ₂ O ₃	700	6	—	CH ₄ : 87	0.3 g _{coke} ⁻¹ g _{cat} ⁻¹ h ⁻¹ (ref. 75)
	800	100	CH ₄ /CO ₂ /He = 10/10/80	CO ₂ : 91	
	800	100	CH ₄ /CO ₂ /He = 1/1.05/1	CH ₄ : 94	0.28 g _{coke} ⁻¹ g _{cat} ⁻¹ h ⁻¹ (ref. 76)
Ni/SiO ₂	700	100	2500 mL g ⁻¹ h ⁻¹	CO ₂ : 94	
			CH ₄ /CO ₂ = 1/1	CH ₄ : 90	0.015 g _{coke} ⁻¹ g _{cat} ⁻¹ h ⁻¹ (ref. 77)
Ni/SBA-15	650	12	72 L g ⁻¹ h ⁻¹	CO ₂ : 88	
	800	50	CH ₄ /CO ₂ /N ₂ = 1/1/1	CH ₄ : 80	No carbon filaments by TEM ⁷⁸
			3824 L g ⁻¹ h ⁻¹	CO ₂ : 85	
			CH ₄ /CO ₂ /Ar = 0.5/0.5/9	CH ₄ : 77	No structured carbon species by TEM ⁴⁸
			22.5 L g ⁻¹ h ⁻¹	CO ₂ : 77	
Ni/MCF	650	4	CH ₄ /CO ₂ = 1/1	CH ₄ : 85	No small amount of carbon deposition by TEM ⁴⁹
			36 L g ⁻¹ h ⁻¹	CO ₂ : 91	A small amount of carbon nanotubes by TEM ²⁶
Ni/HTNT	700	5	CH ₄ /CO ₂ /N ₂ = 1/1/1 (diluted at 10% each in Ar)	CH ₄ : 56	Carbon filaments around the Ni nanoparticles by TEM ⁷⁹
Ni/NaTNT	700	5	12 L g ⁻¹ h ⁻¹	CO ₂ : 70	
			CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 50	
Ni/La ₂ O ₃	700	50	12 L g ⁻¹ h ⁻¹	CO ₂ : 48	
			CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 79	
Ni–Mo/MgO	800	500	60 L g ⁻¹ h ⁻¹	CO ₂ : 78	
			CH ₄ /CO ₂ /N ₂ = 15/15/70	CH ₄ : 70	
			300 L g ⁻¹ h ⁻¹	CO ₂ : 75	
			CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 80	5.47 × 10 ⁻⁵ mmol g _{cat} ⁻¹ s ⁻¹ (ref. 65)
Ni/CaO	Carbonation: 600	10	The CO ₂ flow of 2 mL min ⁻¹ for 6 min	CO ₂ : 80	No carbon deposited by Raman spectra ¹
	DRM: 800		The CH ₄ flow of 2 mL min ⁻¹ for 6 min	CH ₄ : 88	Filamentous carbon by TGA ⁸⁰
	650	1000 min	Carbonation: CO ₂ /N ₂ = 10%	CO ₂ : 59	
			DRM: CH ₄ /N ₂ = 5%	CH ₄ : 96	
Ni/HAP	800	200	40 L g ⁻¹ h ⁻¹	CO ₂ : 96.5	No carbon deposition by Raman spectra ⁸¹
	800	200	CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 93.27	No carbon deposition by Raman spectra ⁸²
			30 L g ⁻¹ h ⁻¹	CO ₂ : 78.38	
			CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 95.28	
Ni–Co/HAP	750	60	CH ₄ (20 vol%) and CO ₂ (20 vol%) diluted in N ₂ (total gas flow rate of 90 mL min ⁻¹)	CO ₂ : 94.94	
			CH ₄ (20 vol%) and CO ₂ (20 vol%) diluted in N ₂ (total gas flow rate of 90 mL min ⁻¹)	CH ₄ : 73	No deposited carbon observed by TGA ¹²
				CO ₂ : 79	Only few carbonaceous species by TEM ⁸³

^a GHSV refers to gas hour space velocity, which is calculated based on the Ni weight of the catalysts.



interface to Ni aggregation. Secondly, it is difficult to form Ni–O–Si bonds in acidic conditions required for the materials synthesis where the Ni particles have higher propensity for aggregation.^{88,89} To solve these issues, researchers have turned to 2-dimensional and 3-dimensional silica. SBA-15 is a type of 2-dimensional silica distinguished by high specific surface areas, large pore sizes and space to support metal catalysts. The existence of silanol groups make them excellent candidates.^{22,24,48} Mesocellular silica foam (MCF) is another material developed from SBA-15 to address the challenges of forming Ni–O–Si bonds.^{26,90} It has a three-dimensional structure with a large uniform spherical cell and an open structure that favors mass transfer.⁹¹ The Ni/SBA-15 (ref. 49) and Ni/MCF²⁶ catalysts presented excellent resistance to sintering and carbon deposition. The nickel particles are reconstituted to form small Ni particles that are evenly dispersed. It not only allows high dispersion and stabilization of nickel metal but also enhances the homogeneity and increases the accessibility to the active sites that is contributed by their specific textural feature.²⁶

However, these supports do not take part in the DRM reaction; both CH₄ and CO₂ activation sites are on the nickel atoms,⁹² which is called monofunctional mechanism,²⁴ resulting in the competed reactions, and thus would finally decrease the DRM reaction rate. To avoid the inactivation by this way, researchers have turned attention to materials that make CH₄ dissociation and CO₂ activation occur at different sites, which is called bifunctional mechanism, where CH₄ dissociation occurs on Ni active sites and CO₂ activation occurs on the supports.²⁴ Titanate nanotubes (TNTs) are famous for their high specific surface area with high aspect ratio titanate nanostructures.⁹³ By the acid wash process, the protonated form (HTNT) can be replaced by Na atoms (NaTNT). Methane dissociation occurs on nickel sites while CO₂ activation occurs on the titanate nanotube supports over Ni/HTNT and Ni/NaTNT (Fig. 6). Ni–NaTNT displayed great coking resistance. It can be explained that the Na⁺ could migrate from the supports to nickel particles and inhibit carbon deposition.⁷⁹ Despite the replacement of Na⁺ improving the number of actives sites for DRM in the titanate nanotubes, it has proven that the interaction of Na⁺ and Ni particles may lower the conversion.⁷⁹

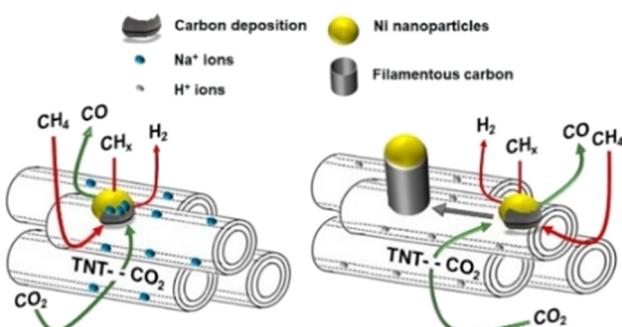


Fig. 6 Schematic diagram of the DRM catalysed by Ni-NaTNT (left) and Ni-HTNT (right). Reproduced from ref. 79 with permission from Fuel, copyright 2019.

Generally, the surface acidity and basicity also play a significant role in the performance of the catalyst for DRM.^{94,95} Coking is more prone to be induced by the supports with acidity, and CO₂ activation is more prone to be introduced by basic supports because of the mild acidity of CO₂.⁹⁶ Ni/La₂O₃ follows the bifunctional mechanism and La₂O₃ reacts with CO₂, accompanied by the formation of La₂O₂CO₃, thus suppressing carbon deposition. La₂O₂CO₃ can react with the deposited carbon to form CO and regenerate La₂O₃.⁹⁷ To overcome the poor dispersion of active metal on the La₂O₃ surface, La₂O₂CO₃ is used as the support precursor because this material would transform to La₂O₃ and La(OH)₃ with the nanorod shape maintained in the synthesis process, which enhanced the anti-coking ability of the catalysts.^{58,65} La₂O₃ adsorbed CO₂, forming La₂O₂CO₃ (CO₂ + La₂O₃ → La₂O₂CO₃), and then La₂O₂CO₃ reacted with C* from the CH₄ dissociation to regenerate La₂O₃ with CO (La₂O₂CO₃ + C* → CO + La₂O₃). By this mechanism, Ni/La₂O₃ would participate in the reaction with filamentous coke, inhibiting the transformation from filamentous coke to non-filamentous coke, which would cover the nickel active sites and cause a decrease in the activity and stability of DRM.⁹⁸

Besides La₂O₃, Ni/MgO catalysts have also been widely recognized as efficient catalysts for DRM.^{99–102} The “Nanocatalysts On Single Crystal Edges” (NOSCE) technique was proposed according to the phenomenon that the Ni particle size was smaller in the initial reaction step and grew larger in the DRM reaction within a few moments (1 hour) but was locked on the same size after prolonged activity (500 hours).¹ The modification is that the particulates move onto the high-energy step edges of the crystalline MgO (111) to form stable particles. This also prevents further sintering while eliminating the risk of MgO participation in the catalytic reaction by the coverage of high-energy step edges.¹⁰³ Similarly, calcium oxide (CaO) is an excellent support because it is low-cost^{104,105} and has a high adsorption property toward CO₂ (~786 g of CO₂ per kg of CaO (ref. 106 and 107)). The CaO support would make the catalyst size larger, but the conversion remains stable because CaO could eliminate the deposited carbon.⁸⁰ Firstly, the CO₂ was captured by CaO and formed CaCO₃, illustrated as *CO₂. Then the captured *CO₂ reacts with deposited carbon on the CaO–Ni interface (*CO₂ + C → 2CO), eliminating the carbon deposition. The temperature at which H₂ generation from CH₄ dissociation was appreciably lower than that of CO formation indicates that the interface is more inclined to activate CH₄ than CO₂.²⁷ As previously mentioned, CH₄ dissociation on Ni sites follows this rule: *CH₄ → *CH₃ + *H → *CH₂ + *H → *CH + *H, then the produced *H consequently combine and form H₂. But the presence of CO₂ captured by CaO could make *H participate in the CO₂ conversion by producing *COOH, which would dissolve into *CO and *OH. It is called *H-assisted *CO₂ conversion. Subsequently, the *OH could participate in CH₄ dehydrogenation through this way: *CH₂ + *OH → *CH₂OH → *CH₂O + *H → *CHO + *H → *CO + *H. Therefore, the



overflow of $^*\text{OH}$ produced in the $^*\text{H}$ -assisted $^*\text{CO}_2$ conversion can accelerate CH_4 dehydrogenation, and this is named $^*\text{OH}$ -assisted CH_4 dissociation. By this synergistic promotion, the coking resistance was improved significantly.^{34,81}

Temperature-programmed reactions were employed to identify CH_4 dehydrogenation and CO_2 activation involved in the DRM process. Although the addition of CaO could enhance the DRM anti-coking ability over the Ni-based catalyst, the reaction ability decreases with the cycle number due to the sintering of materials. To get catalysts with anti-sintering and great performance for DRM over Ni/CaO , not only are the reduction of carbonates and CH_4 dissociation but also the trade-off of the density of Ni nanoparticles and its size are required to be taken into consideration to achieve the expected adsorptive/catalytic interface as the increase in Ni nanoparticles would cause increased average sizes of Ni nanoparticles and decreased specific surface area.^{81,108}

In addition to the supports mentioned above that enhance the performance of DRM over Ni-based catalysts by metal-support interaction, Ni particles can form a structure of solid solution by replacing the metal atoms on the supports, which contributes to homogeneously dispersed Ni nanoparticles. Hydroxyapatite (HAP, $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$) is a weak alkaline calcium phosphate.^{82,83,109} It has strong modifiable properties, where the Ni nanoparticles replace the external Ca atoms in HAP owing to its capability of forming hydroxyapatite structures over a wide Ca/P range, and the hydroxyl groups in HAP can oxidize the carbon formed by CH_4 dissociation.^{12,110} HAP-D (HAP-D refers to the HAP inherently without Ca) facilitates a robust anchor positioning for the Ni particles and enhances the oxygen migration of hydroxyl groups in HAP. A novel scheme (Fig. 7) was proposed where CH_4 dissociation is more inclined to CH_3O following dehydrating to CO without coking rather than cleaving the bonds of C-H to carbon deposition. Subsequently, the oxygen vacancies generated are replenished through the dissociation of adsorbed CO_2 as they are refilled with oxygen atoms. Undoubtedly, the matching between the rate of progressive cleavage of CH_4 on the metal and the rate of the intermediate cleavage

products oxidized by the oxygen atoms in the support plays a critical role in determining the performance. Also, the matching between the two aspects is much better for Ni/HAP without the problem of coking.¹¹¹

Promoter selectivity

The performance of Ni-based catalyst in the DRM reaction is not decided only by the Ni particles dispersed on the support but also the promoter.^{30,112} Depending on the species, promoters applied in DRM over Ni-based catalysts could be normally divided into metals and rare earth metallic oxides. These promoters can not only regulate the physical (changing the electronic density, maintaining small particle size in reaction, and affecting the catalytic surface acidity and basicity) and chemical (providing oxygen vacancies and enhancing the MSI) properties of the nickel particles but also participate in the process of CH_4 dissociation or CO_2 adsorption, thereby improving the performance or enhancing the resistance to carbon deposition.¹¹³

Metals

Diverse metals are employed to enhance the catalytic activity and selectivity as well as to prevent the sintering of nickel particles.¹³ Table 4 summarizes the reaction conditions and CH_4 and CO_2 conversions by different metal promoters.

Metals such as Co and La have a beneficial effect on nickel-based catalysts by alloying with nickel particles, which is typically attributed to the similar surface electronical and geometric chemistry with nickel particles.^{13,114} Based on *in situ* XPS analysis, the doped metals (Co, La) donate electrons to the Ni atoms, changing the chemical properties by lowering the Ni average valence state and enhancing the CO_2 dissociation process.^{38,115} The formed Ni-Co solid solution alloy can not only favor the reduction of the nickel species to Ni^0 by increasing the active sites in the fresh $\text{Ni}-\text{Co}/\text{Al}_2\text{O}_3-\text{S}$ catalyst³⁸ but also improve the CO_2 dissociation ability with a high Ni average valence state in carbonation (Fig. 8B), which would subsequently react with C^* and promote H_2 desorption at lower temperature (Fig. 8D). It inhibited the side RWGS reaction to give a high H_2/CO ratio.³⁸ However, in the last reaction cycles, the Co doped in the catalyst is more prone to oxidize the Ni particles to NiO , the inactive sites which decrease the catalytic activity.⁴⁰ Thus, the self-oxidation process is a main challenge for the method of Co modification. Both the nickel valence state and the formation of solid solution alloy may strengthen the MSI.¹¹⁶ Ni-La bimetallic catalysts have been extensively researched for enhancing the carbon resistance and activity of DRM. The presence of La promotes the formation of 1:1 and Tran-2:1 nickel phyllosilicate, revealing a robust interaction with the SiO_2 support. This strong interaction ensured a high reduction degree (Ni^0) of Ni particles. Thus, sufficient nickel particles are exposed with basic sites in $\text{Ni}-\text{La}/\text{SiO}_2$ interface, which favors the removal of coking, and this is the important cause for the attenuation of catalyst deactivation.^{117,118}

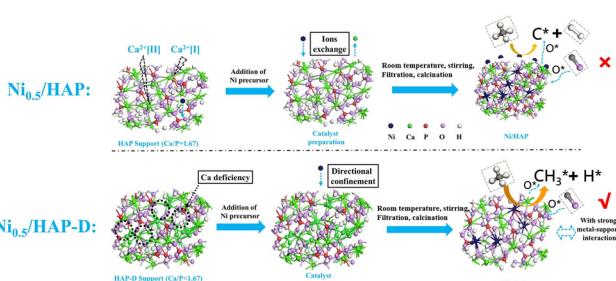


Fig. 7 Schematic diagram of catalyst synthesis path and DRM reaction route. Reproduced from ref. 12 with permission from Fuel, copyright 2022.



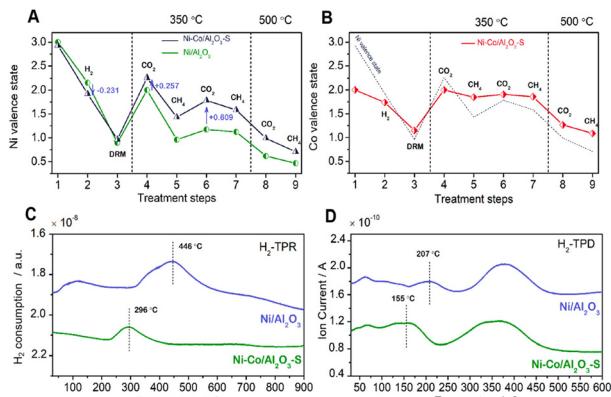


Fig. 8 Ni average state change of (A) Ni/Al₂O₃ and Ni-Co/Al₂O₃-S (prepared by stepwise impregnation) and Co average state change of (B) Ni-Co/Al₂O₃-S catalyst (with Ni average state change as a reference (dashed line)) with different treatment steps: (1) the as-prepared catalysts; (2) after reduction in hydrogen at 300 °C; (3) after DRM reaction at 800 °C; (4–7) sequential treatment with CO₂ (4 and 6) or CH₄ (5 and 7) at 350 °C; (8 and 9) sequential treatment with CO₂ or CH₄ at 500 °C. H₂-TPR (C) and H₂-TPD (D) results of Ni/Al₂O₃ and Ni-Co/Al₂O₃-S catalysts. Reproduced from ref. 38 with permission from American Chemical Society Catalysis, copyright 2019.

It is worth noting that the metals are also favorable for increasing the activity and resistance to carbon deposition by effecting the process of CO₂ activation.^{119,120} Gadolinium (Gd) has the capacity to generate oxygen vacancies, serving as active sites to adsorb CO₂. This facilitates the extraction of oxygen from CO₂, thereby promoting the dynamics of the DRM reaction.^{121,122} The promotional effect of Gd could be contributed to the formation of Gd₂O₂CO₃, facilitating the CO₂ adsorption and activation. Along with this, Gd also maintains the size of Ni particles by further promoting the stability.¹²³ Meanwhile, Sc in the optimum range strengthened the interaction of Ni with the support. This enhancement of basicity subsequently influences the quantity of CO₂ adsorbed on the catalytic surface, thus improving the DRM performance.¹²⁴

On the other hand, Ni particles are easily oxidized to NiO during the process of CO₂ reduction. To slow down the deactivation, some transition metal elements are doped into the catalysts, inhibiting the oxidation of Ni sites. Taking molybdenum (Mo) for example, both CH₄ and CO₂ conversion of catalysts with Mo was much higher than the ones without Mo.¹ According to the shifts of Ni peaks (Fig. 9), it is reasonable that there is a process of electron transfer from nickel atoms to Mo atoms within the alloy structure, revealing the strong electronic interaction between Mo and Ni.¹²⁵ It indicates that the Mo shows more affinity to *O than Ni, which is consistent with the DFT results (Fig. 10). At the same time, Mo also provides unique dynamic variation of MoO_x → MoC_xO_y, enabling efficient carbon elimination during the DRM reaction.

Besides the process of CO₂ activation, the associative “formate” mechanism is also displayed for some other metals. To eliminate the carbon deposition, it is attractive to turn the CH₄ dissociation intermediates of carbonate species

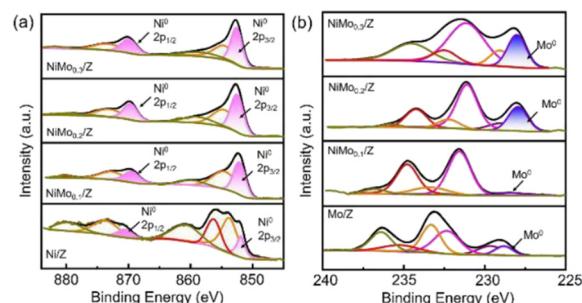


Fig. 9 The *ex situ* spectra (a) Ni⁰ 2p and (b) Mo⁰ 3d XPS spectra of the reduced catalysts. Reproduced from ref. 125 with permission from American Chemical Society Catalysis, copyright 2021.

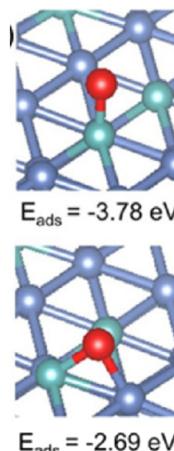


Fig. 10 Oxygen adsorption energy on NiMo(111) (Ni: blue, Mo: green, O: red). Reproduced from ref. 125 with permission from American Chemical Society Catalysis, copyright 2021.

(*CH_x) to formate species (HCOO*), which can be achieved by metals like Mo (ref. 125) and Cs.¹²⁶ According to the DFT calculation, the high carbon deposition resistance is attributed to the well-dispersed Cs dopants, which suppress *CH dehydrogenation (*CH → C + *H) where the *C is commonly considered as the precursor to carbon deposition, and enhance the *CH oxidation (*CH + *O → *CHO). The Cs dopants increased the energy difference to 0.1 eV between *CH dehydrogenation and *CH oxidation. This leads to more favorable *CH oxidation, whereas these two processes (*CH dehydrogenation and *CH oxidation) simultaneously occurred in the catalysts without Cs doping.

Another significant aspect of promotion is to decelerate the rate of CH₄ dehydrogenation and concomitantly accelerate carbon gasification. According to DFT calculation, the promotion of Fe (ref. 127) and Pt (ref. 128) in Ni-based catalysts increases the kinetic barrier for CH₄ activation, simultaneously decelerating the rate of carbon deposition. Moreover, Fe enables the nickel size into small ensembles, while the coking resistance is notably better with small particles due to the hindrance of surface carbon deposition.^{127,129} By the way, Fe is oxyphilic and could be oxidized by CO₂ to FeO (CO₂ + Fe → CO + FeO), then the



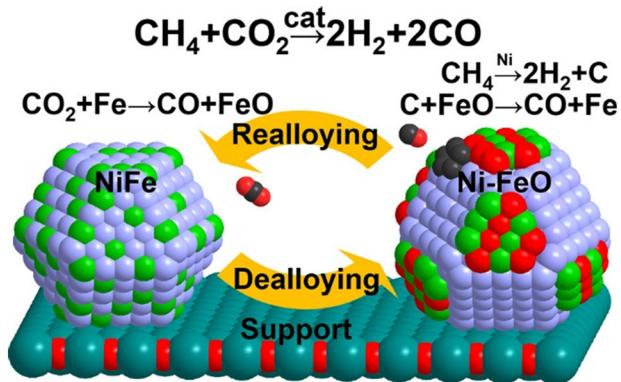


Fig. 11 De-alloying and re-alloying behaviour of a Fe-Ni-alloyed particle during the dry reforming of methane. Reproduced from ref. 130 with permission from Journal of American Chemical Society, copyright 2017.

carbon formed by CH_4 dissociation is oxidized to CO by the lattice oxygen from FeO ($\text{C} + \text{FeO} \rightarrow \text{CO} + \text{Fe}$) (Fig. 11).^{61,71,130} In a conclusion, the effect of Fe can be attributed to the following: (a) slow down the coking rate and concomitantly accelerate the carbon gasification rate; (b) enable small nickel size to change the carbon species to a type easily oxidized; (c) increase the oxyphilic property of the material.

To achieve excellent promotion, metal loadings is an important factor that must be considered. A low content would minimize the promotion, whereas a high content would cause a decrease in the conversion resulting from the coverage of active sites by the metals. Taking Fe as an example, the Fe/Ni ratio significantly determines the promotion or suppression of the catalytic activity. When the molar ratio is above 0.9, the mesoporous structure would be destroyed, thus decreasing the catalytic activity, whereas the activity of catalysts is the highest and the deactivation is the lowest when the molar ratio is 0.7.¹³¹ Besides Fe, scandium (Sc) also faces the same problem. The optimum range of Sc loading was 0.1–0.5%. An Sc content above 0.5% would cover the Ni active sites and result in a decrease in CH_4 and CO_2 conversion.⁶⁹

In general, the scarce information concerning the role of transition metals in DRM is largely due to the absence of techniques capable of concurrently examining the alteration in electronic structure and visualizing the morphology of the active sites under the operational conditions.¹¹⁵ This challenge remains and inhibits the further understanding and study of synthesizing catalysts with superior properties.

Rare earth metallic oxide

In recent years, rare earth metallic oxides as promoters have attracted attention for the enhancement in CO_2 adsorption and activation to produce CO by maximizing the catalytic oxygen vacancies.¹²⁹ The vacancies are normally raised from the inherent point defects on metallic oxide catalysts exposed to elevated temperatures and a reducing atmosphere.¹³² The oxygen vacancies are the potential sites for the adsorption

and activation of CO_2 .^{133,134} The mobile oxygen on the catalyst surface can react with $^*\text{C}$ and form CO and is in turn filled by the oxygen from the adsorbed CO_2 dissociation.^{23,39,40} The process of DRM on the Ni-based catalysts with oxygen vacancies includes the following steps (Table 3): a) oxygen migration from the rare earth metallic surface ($\text{O}_{\text{CGO}}^{\text{surface}}$) to the nickel surface (O_{Ni}^*) (eqn (10)); b) methane decomposition into carbon and hydrogen (H_2) at the Ni sites (eqn (11)); c) methane oxidation into CO_2 with the production of H_2O (this process only occurs when the oxidation state of the ceria is high) (eqn (12)); d) decomposed carbon oxidation partially into CO (eqn (13)); e) oxygen migration from bulk ($\text{O}_{\text{CGO}}^{\text{bulk}}$) to surface ($\text{O}_{\text{CGO}}^{\text{surface}}$) (eqn (14)); f) amorphous carbon ($\text{C}_{\text{amorphous}}$) formation (eqn (15)).^{135–137} Table 5 summarizes the reaction conditions and CH_4 and CO_2 conversions by different rare earth metallic oxides.

Ceria (Ce) and ceria-containing materials have been extensively applied for DRM over Ni-based catalysts. This is attributed to their feasible reducibility and high oxygen storage capacity (OSC). They can switch between Ce^{3+} and Ce^{4+} with the variation of oxygen vacancies. They favour forming Ce^{3+} with the formation of oxygen vacancies at a high temperature.¹⁴⁰ Ceria doped with lower valence state has the advantage of exhibiting high oxygen mobility and the capacity to retain its crystal structure with a significant degree of ceria reduction, which contributes to improved carbon deposition resistance.¹³⁶ To analyse the activity–structure relationship in detail, a facile methane transient pulse experiment was conducted under the ambient pressure to test the impregnated Ni-Gd/CeO₂ (Ni/CGO) (Fig. 12).^{135,141} It has founded that there are two competing oxidation processes for CO production.³⁴ The first one is methane dehydrogenation and carbon species (C/CH_x) being oxidized by the oxygen vacancies from CGO. The second one is where C/CH_x is oxidized by the oxygen ions migrating from the bulk of CGO after the surface oxygen is exhausted. Thus, there is no carbon deposition if the time is long enough to allow oxygen migration. Meanwhile, a low concentration of steam can replenish the surface oxidation states, which controlled the oxygen migration and CO selectivity without influencing the ability and stability of DRM.^{135,136}

ZrO_2 has high stability and surface oxygen mobility.¹⁴² It has been applied in the DRM as promoter¹⁴³ or support,^{144,145} contributing to its chemical properties of

Table 3 The reaction of oxygen vacancies

Equation	Reaction equation
10	$\text{O}_{\text{Ni}}^{\text{surface}} \rightarrow \text{O}_{\text{Ni}}^*$
11	$\text{CH}_4 + \text{O}_{\text{Ni}}^* \rightarrow \text{C} + 2\text{H}_2$
12	$\text{CH}_4 + \text{O}_{\text{Ni}}^* \rightarrow \text{CO} + 2\text{H}_2\text{O}$
13	$\text{C} + \text{O}_{\text{Ni}}^* \rightarrow \text{CO}_{\text{(g)}}$
14	$\text{O}_{\text{CGO}}^{\text{bulk}} \rightarrow \text{O}_{\text{CGO}}^{\text{surface}}$
15	$\text{C}_{\text{Ni}}^* \rightarrow \text{C}_{\text{amorphous}}$
16	$\text{C}/\text{CH}_x + \text{O}_{\text{surface}}^* \rightarrow \text{CO} + \text{H}$



Table 4 Performance of Ni-based catalysts doped by different metal species for DRM reaction

Catalyst	Temp (°C)	Time (h)	GHSV and feed gas radio	Conversion (%)	Carbon deposition
Ni-Co/γ-Al ₂ O ₃	800	15	Flow rate: 490 mL min ⁻¹ A gas mixture of 7% CH ₄ and 9.5% CO ₂ in N ₂	CH ₄ : 79 CO ₂ : 71	Filamentous carbon formed by STEM ¹¹⁵
Ni-Co/Ce _{0.75} Zr _{0.25} O _{2-δ}	750	20	25 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1/1 = 3	CH ₄ : 60 CO ₂ : –	Low carbon deposition ⁴⁰
Ni-Co/Al ₂ O ₃ -S	800	60	998.4 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1/1/8	CH ₄ : 92 CO ₂ : –	No surface carbonate by XPS ³⁸
Ni-Co-Al-Mg-O	750	250	180 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1/1/1	CH ₄ : 0/64 mmol g _{cat} ⁻¹	No carbon formation by TG ¹¹⁴
Ni-Gd/MCM	800	400 min	39 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ = 1/1	CH ₄ : 87.6 CO ₂ : 91.7	No carbon formation by TG ¹²³
Ni-GDC ^a	800	100	28 800 h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1/1/1	CH ₄ : 95 CO ₂ : 95	Graphitic carbon by TGA ¹²¹
Ni-Sc/MCM-41	800	400 min	39 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ = 1/1	CH ₄ : 85 CO ₂ : 90	Carbon deposition decreased by TGA ⁶⁹
Ni-Mo/CaO	750	500	300 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 50/50/20 mL min ⁻¹	CH ₄ : 81 CO ₂ : 75	No filaments carbon by TEM ¹
Ni-Mo/ZSM-5	750	200	50 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ = 50/50 mL min ⁻¹	CH ₄ : 90 CO ₂ : 96	16.8 mmol _C mol _{surfaceNi} ⁻¹ h ⁻¹ (ref. 125)
Ni-Cs/Al ₂ O ₃	800	250 min	72 N L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1:1:2	CH ₄ : 89.8 CO ₂ : 91.8	No carbon deposition by TEM ¹²⁶
Ni-Fe/MgO	800	100	86 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ = 1/1	CH ₄ : 89 CO ₂ : 93	18.84 mol% ^b ¹²⁷
Ni-Fe/LSTIN ^c	900	400	30 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /He = 10:10:80 mL min ⁻¹	CH ₄ reactivity = 1.65 × 10 ^{19d}	Not mentioned ¹³⁸
Ni-Fe/MA	650	5	270 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 45/45/10	CH ₄ consumption = 20.4 mmol g _{cat} ⁻¹ min ⁻¹	18 wt% ¹³⁰
Ni-Fe/MgAl ₂ O ₄	800	250 min	1 mL s ⁻¹ CH ₄ /CO ₂ = 1/1	CH ₄ : 51 —	Filamentous carbon deposition by TSG ⁷¹
Ni-Pt/Ce _{0.8} Pr _{0.2} O _{2-δ}	750	50	30 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /He = 20/20/60	CH ₄ : 95 —	0.13 mg g _{cat} ⁻¹ (ref. 128)
Ni-Pt/CeZrO ₂	800	15	120 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /He = 10/10/20 mL min ⁻¹	CH ₄ : 93 CO ₂ : 96	Carbon deposition by TGA ¹³⁹

^a GDC refers Ce_{0.8}Gd_{0.2}O_{2-δ}. ^b It represents catalyst surface carbon coverage radio. ^c It represents La_{0.6}Sr_{0.2}Ti_{0.85}Ni_{0.15}O_{2.95}.

$$d \text{CH}_4\text{reactivity} \left[\frac{\text{molecules}}{\text{s} \times \text{g}_{\text{cat}}} \right] = \frac{\text{H}_2\text{detect} [\text{molecules per s}]}{2 \times \text{weight of catalyst [g]}}$$

basicity, which is beneficial for the elimination of deposited carbon by the mobile oxygen from the surface oxygen

vacancies.^{146,147} The oxygen vacancies of ZrO₂ include the oxygen species (Table 6) such as the lattice oxygen (O_l) and

Table 5 Performance of Ni-based catalysts doped by rare earth metallic oxide species for DRM reaction

Catalyst	Temp (°C)	Time (h)	GHSV and feed gas radio	Conversion (%)	Carbon deposition
Ni-CeO ₂ /Al ₂ O ₃	800	72	CH ₄ /CO ₂ = 45/45 mL min ⁻¹	CH ₄ : 78 CO ₂ : 81	60 mg _C g _{cat} ⁻¹ (ref. 39)
Ni/CeO ₂	700	30	CH ₄ /CO ₂ /Ar = 20/20/60 mL min ⁻¹	CH ₄ : 44 CO ₂ : 57	Negligible amount of carbon with graphitic form by XRD ¹⁴⁹
Ni-Co/CeO ₂	700	5	1 atm, 50 sccm CH ₄ /CO ₂ /Ar = 1/1/3 ^a	CH ₄ : 70 CO ₂ : 70	Carbon filaments by HCTEM ¹⁴⁰
Ni/CeO ₂	750	10	2700 L g ⁻¹ h ⁻¹ A gas mixture of 50%Ar:25%CH ₄ :25%CO ₂ (volume)	CH ₄ : 94 CO ₂ : –	Carbon nanofiber by SEM ¹³⁶
Ni-CeO ₂ /MgO	800	12	720 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /N ₂ = 1/1/1	CH ₄ : 78 CO ₂ : –	Carbon deposition suppressed by XRD ¹⁵⁰
Ni-CeO ₂ /HAP	750	7	60 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ /He = 10/10/30, total flow = 50 mL h ⁻¹	CH ₄ : 82 CO ₂ : 78	Negligible carbon deposition by TGA ¹⁵¹
Ni/ZrO ₂	700	5	24 L g ⁻¹ h ⁻¹ CH ₄ /CO ₂ = 1/1	CH ₄ : 51 CO ₂ : 62	Carbon formation by TG ¹⁴⁶

^a SCCM refers to the standard cubic centimeter per minute.



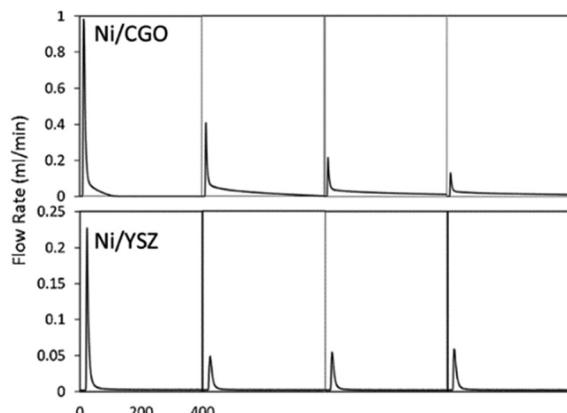


Fig. 12 The first to fourth CO production peak of a methane pulse on Ni/CGO and on Ni/YSZ. Reproduced from ref. 135 with permission from Applied Catalysis B: Environmental, copyright 2019.

Table 6 XPS fitting results of ZrO_2 samples after treatment under different atmospheres

Treatment atmosphere	The lattice oxygen (O_{I}) area (%)	The adsorbed oxygen (O_{II}) area (%)	$\text{O}_{\text{II}}/\text{O}_{\text{I}}$
H_2	58.57	41.43	0.71
N_2	60.25	39.75	0.66
O_2	63.61	36.39	0.57

the adsorbed oxygen (O_{II}).^{92,148} O_{II} is favorable for promoting both CO_2 adsorption activation and CH_4 dissociation by changing the surface acidity and basicity. To increase the radio of $\text{O}_{\text{II}}/\text{O}_{\text{I}}$, the Ni/ZrO_2 materials can be treated with H_2 atmosphere.

Preparation

Using unconventional preparation methods or changing the reaction process to modify the interaction between metals and supports has always been a challenging issue.

Impregnation

Impregnation (IM) method is an effective synthesis method. Table 7 summarizes the properties and performance of the

catalysts prepared by IM. In the impregnation method, the active solid precursor is immersed in a solution of certain concentration of the active phase precursor for different periods, and then the solution is dried subsequently.¹⁵² According to the amounts of solution, the IM can be categorized into wet impregnation (WI) and incipient wetness impregnation (IWI). WI uses an excess solution while IWI uses a limited amount of solution where the volume of the solution is approximately equal or slightly lower than that of the solid.¹⁵³ Due to the restricted solution diffusion in the catalyst pores, IWI produces the least dispersed metal particles, whereas WI produces more dispersed particles due to the excess solvent.^{12,154}

Generally, in the catalysts prepared by IM, the nickel particles has weak MSI and may be located in the exterior pores.¹⁶⁰ The nickel active sites are easily carried away with steam. In most instances, the catalysts are tested as control groups with other catalysts from evaporation-induced self-assembly and sol-gel methods. Some researchers also perform pretreatment before the catalysts are experimented in the DRM process. With hydrogen treatment before the calcination, the synthesized Ni/SiO_2 were highly dispersed and uniformly distributed with the availability of small Ni particles with a strong MSI. This was attributed to the elimination of oxygen in the hydrogen treatment, and (phyllo)silicate structure was formed in the following calcination process.⁷⁸

Evaporation-induced self-assembly

Table 8 summarizes the properties and performance of the catalysts prepared by the evaporation-induced self-assembly (EISA) method. This method involves the continuous mixing of the solution with the structure-directing agents (SDA), followed by the evaporation and the initiation of co-assembly with ordered mesopores.¹⁵⁴ Fig. 13 depicts the steps involved in the preparation of the materials.¹⁶¹

The formed mesoporous catalysts are highly active and stable, with the support pore size of 3–5 nm after reaction for 30 h, whereas the pore size increased to 12 nm for the catalysts without the assistance of spray pyrolysis. The difference in size would further influence the carbon resistance, where the filamentous carbon was more difficult to form on the surface of catalysts with spray pyrolysis.¹⁵⁵

Table 7 The catalysts prepared by IM methods

Catalyst	Method	Nickel loading (wt%)	Particle size (nm)	Time (h)	CH_4 conversion (%)	CO_2 conversion (%)	Ref.
$\text{Ni}/\text{Al}_2\text{O}_3$	IM	6	12.5	100	80	78	148
$\text{Ni}/\text{Al}_2\text{O}_3$	IM	10	12.6	30	68	79	155
$\text{Ni}/\text{Al}_2\text{O}_3$	IM	12	24.5	80	55	70	156
$\text{Ni}/\text{Al}_2\text{O}_3$	IM	5	—	20	58	70	52
Ni/SiO_2	IM	5	6	20	82	89	52
$\text{Ni}-\text{CeO}_2/\text{Al}_2\text{O}_3$	IM	7	6.9	80	47	72	157
Ni/SiO_2	IM	5	18	200	30	45	158
Ni/HMS^a	IM	5	16.5	100	64	41	159

^a HMS refers to hexagonal mesoporous silica.



Table 8 The catalysts prepared by EISA methods

Catalyst	Method	Nickel loading (wt%)	Particle size (nm)	Time (h)	CH ₄ conversion (%)	CO ₂ conversion (%)	Ref.
Ni/Al ₂ O ₃	EISA	6	11.2	100	94	90	162
	EISA	10	3	30	93	98	155
	EISA	12	15.6	80	92	91	156
Ni@SiO ₂ ^a	EISA	5	4.3	20	90	90	52
Ni-CeO ₂ /Al ₂ O ₃	EISA	7	5.2	80	83	85	157
Ni/SiO ₂	EISA	5	5	200	79	70	158
Ni-HMS ^b	EISA	5	3.90	100	85	77	159

^a The materials have a core-shell structure.

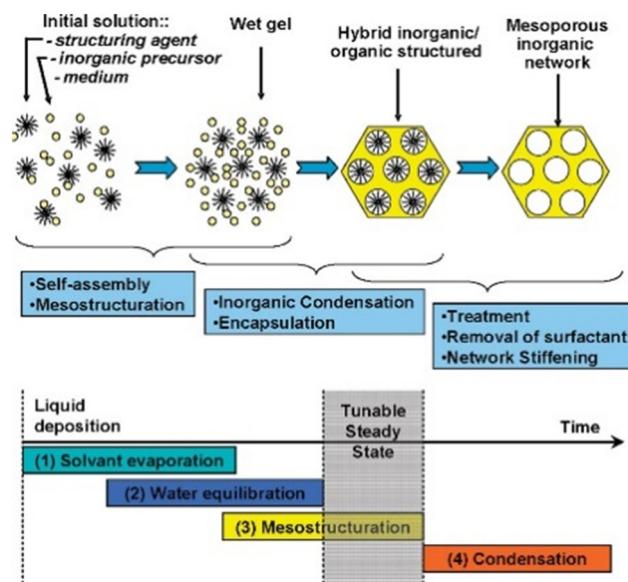


Fig. 13 The scheme process of the EISA method. Reproduced from ref. 161 with permission from Chemical of materials, copyright 2008.

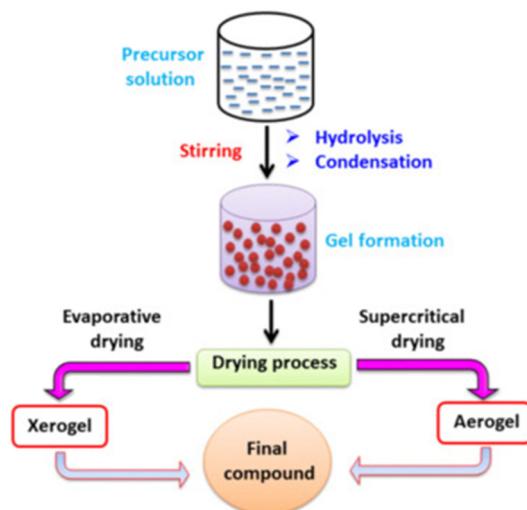


Fig. 14 The scheme process of the sol-gel method. Reproduced from ref. 153 with permission from Journal of Environmental Chemical Engineering, copyright 2021.

Sol-gel method

Table 9 summarizes the properties and performance of the catalysts prepared by the sol-gel method. The sol-gel method (SG) scheme process starts by preparing a gel using precursors and complexing agents. The gel is then dried and pre-treated to form the final compounds as the catalysts (Fig. 14). In general, the particle size is large than those obtained from EISA.¹⁵⁴ Thus, the produced catalysts are

mostly applied in the situation where promoters are added. Generally speaking, the metal (CoNiAl₂O₄,¹⁶³ Ni-Co/Al₂O₃-MgO-ZrO₂,¹⁶⁴ CoWNi/Al₂O₄¹¹), alkaline earth metal oxide (Ni-MgO/Al₂O₃¹⁶⁵) and rare earth metal oxide (Ni-CeO₂/Al₂O₃,^{165,166} Ni/CeO₂¹⁶⁷) could be synthesized *via* the sol-gel method. The detailed mechanism of the promoters has been illustrated in section 3.2.

The plasma treatment is also used in the sol-gel method by producing catalysts of high specific areas, strong MSI, but

Table 9 The catalysts prepared by SG methods

Catalyst	Method	Nickel loading (wt%)	Particle size (nm)	Time (min)	CH ₄ conversion (%)	CO ₂ conversion (%)	Ref.
Ni/Al ₂ O ₃	SG	10	35.3	600	70	—	166
CoNiAl ₂ O ₄	SG	10	14.7	2880	96.5	94.5	163
Ni-Co/Al ₂ O ₃ -MgO-ZrO ₂	SG	10	17.1	1440	58	97	164
CoWNiAl ₂ O ₄	SG	10	27.6	2880	78.5	75	11
Ni-MgO/Al ₂ O ₃	SG	10	24.7	1440	95.0	63.0	165
Ni-CeO ₂ /Al ₂ O ₃	SG	10	23.3	1440	98	99	165
Ni-CeO ₂ /Al ₂ O ₃	SG	10	35.9	600	90	95	166
Ni/CeO ₂	SG	15	11	700	22	28	167
Ni@CeZrO ₂ ^a	SG	10	8	1440	42	54	168

^a The materials are structure of core-shell.

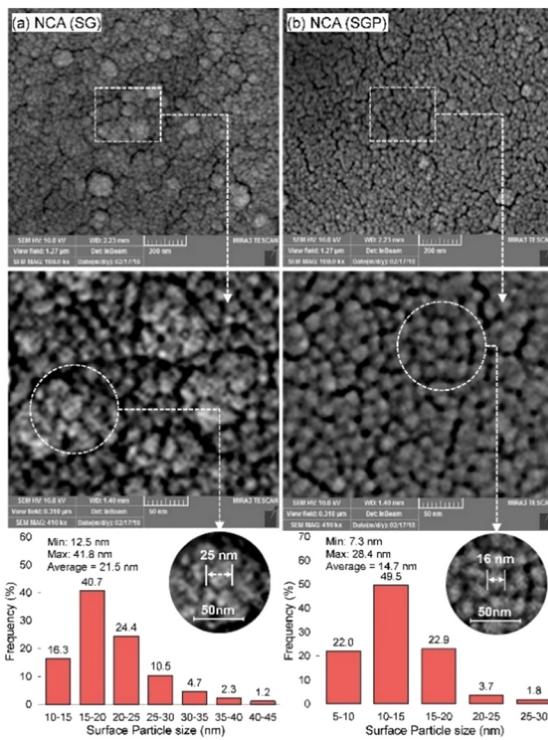


Fig. 15 The surface particle size histogram of Co-promoted Ni-spinel nano-catalysts fabricated via sol-gel and hybrid sol-gel-plasma methods: (a) NCA (SG refers to catalysts from the sol-gel method) and (b) NCA (SGP refers to catalysts from sol-gel-plasma methods). Reproduced from ref. 163 with permission from Chemical Engineering journal, copyright 2019.

small particle size (Fig. 15). NCA (SGP) (refers to Ni–CeO₂/Al₂O₃ from sol-gel-plasma methods) showed great stability with the conversion dropping to 97% after 2880 min. The plasma treatment influenced the crystalline structure that lowered the growth rate of coke aggregation. Meanwhile, high energy species produced during plasma treatment acted as potent reducing agents, participating in both coking gasification and the reduction of the active phases in their oxidized state.¹⁶³

Prospects

Dry reforming of methane (DRM) reaction is currently receiving renewed attentions for carbon capture, utilization & storage (CCUS) owing to its advantages of simultaneous reaction with CH₄ and CO₂ by forming H₂ and CO, which are the ideal products for industries. This review discussed the mechanism of DRM over Ni-based catalysts, the issues and the advances of performance enhancement of the catalysts for the promotion of the technology. Owing to the fact that Ni is an active cost-effective metal for DRM, however, with propensity for sintering and carbon deposition that inhibits its performance, significant strategies have been promoted for strengthening the performance of Ni-based catalysts such as incorporating supports and doping promoters by various synthesis methods.

The effects of supports on catalysts include the confinement and change of active sites. The supports with mesopores structure would improve the dispersion of active sites. It confines the Ni particles by its uneven surface and pore structure, preventing particle sintering in the DRM process. Moreover, some support species tend to promote CO₂ adsorption and activation by offering more CO₂ adsorption sites. These supports are mostly alkaline and widely used to suppress the CO₂ adsorbed on the nickel sites but adsorb on the support sites. It avoids the competing reactions between CH₄ dissociation and CO₂ reduction. Also, it favors CH₄ dehydrogenation to form *COOH and avoids the formation of *C (which is the precursor of deposited carbon). However, it is also worth noting that the ideal supports cannot react with the active sites, otherwise the activation would decrease.

According to the species, the promoters can be divided to two categories, namely, metals and rare earth metallic oxides, based on different functions. The influences of metallic promoters could be attributed to these aspects: (a) increasing the surface area; (b) facilitating CO₂ adsorption and dissociation; (c) inhibiting the side reactions and suppressing CH* dissociation (*CH → *C + *H); (d) maintaining the Ni particle size; (e) modifying the nickel electronic properties and crystal phase. A single metal promoter incorporated into the catalysts usually comprises several of the above aspects. Rare earth metallic oxides have the distinctive characteristic of oxygen vacancies. They favour CO₂ dissociation by offering more adsorbed sites, and the mobile oxygen could react with the carbonates, thus prolonging catalytic lifetime by avoiding coke deposition.

Catalysts prepared by different synthesis methods may present huge differences in the physical and chemical properties. In general, catalysts prepared by EISA and sol-gel methods are normally stable with highly dispersed and small Ni particles strongly interacting with the supports. The catalytic performance of the catalysts prepared from the EISA method largely depends on the type of structure-directing agents (SDA). The vaporization of SDA influences the MSI and consequently affects the activation and stability. On the other hand, the catalysts fabricated by the sol-gel method are featured with larger size (mostly above 10 nm) than those by the EISA and impregnation methods due to the weaker MSI. But the interaction of nickel particles and promoters would be strengthened, and active sites are more dispersed. The impregnation method is a convenient and promising one for catalyst preparation; however, the Ni particles are normally located at the exterior pores of the supports due to the main mechanism of diffusion. To enhance its performance, pre-treatments such as plasma treatment and spray pyrolysis could be used, which have been proven useful in another field.

The morphology, structure and composition are important factors that should be considered to design remarkable Ni-based catalysts. The synergistic effect of support, promoters and various synthesis methods is also an important point required for consideration.



The different performance of catalysts prepared with the same method is attributed to the different reaction conditions (synthesis method, temperature, GHSV, CH_4/CO_2 ratio). This confirms the important role of the reaction conditions in the overall catalytic performance. So, it's necessary to comprehensively design or prepare catalysts by considering all the factors mentioned above and not just the support and promoter separately.

To promote the technology, further research is required in the following areas.

1. Explore more materials with high specific areas or pre-treatment methods for protecting the Ni particles from sintering and carbon deposition. Supports with high specific areas and structures of core-shell or dendrimer morphology can be developed for offering strength and stability of catalysts. Modifying the commercial materials as supports or using pre-treatment such as plasma-treatment and spray pyrolysis also are significant strategies for protecting the Ni particles from sintering and carbon deposition. However, the issue of catalysts deformation or embrittlement at high temperatures still requires special attention.

2. Manipulate the interactions of metal-support and metal-metal by choosing various supports or promoters. Nickel dispersion and size, basicity, oxygen lattice lability and mobility can be influenced by these interactions and are highly beneficial for promoting the catalytic anti-sintering and anti-coking abilities. At the same time, the interaction between promoters and supports in catalysts may influence the nickel electron density and the valence state, and thus the activity and stability.

3. Quantify the critical particle distance for anti-sintering. The significance of particle spacing in the sintering process is noteworthy. However, no existing literature provides an exact quantitation and measurement of the particle spacing at which sintering would be significantly inhibited. This sort of information is vital for the development of catalysts that can effectively resist sintering.

4. Employ more advanced *in situ* techniques for a detailed understanding of the reaction mechanisms. The detection of reaction intermediates other than CH_x species and surface carbon (C_α , C_β , C_γ) remains elusive, and a comprehensive understanding of these unidentified intermediates would greatly contribute to elucidating the identity of crucial reaction intermediates and the detailed reaction pathway. This is essential for the further improvement of the activity and stability for Ni-based catalysts for DRM reactions.

5. Achieve DRM at medium temperatures ($<800^\circ\text{C}$). DRM in medium temperature is a challenging goal and is expected to receive grand attention. The medium temperature would suppress carbon deposition, thus improving the stability of catalysts. However, the reaction rate is also slowed down, with the side reactions occurring as well. Thus, further study is required to understand the mechanism of DRM reactions at low temperatures.

Conflicts of interest

There is no competing financial interest.

Acknowledgements

This work was funded by the National Science Foundation of China – Shanxi Coal – based Low – carbon Joint Fund (U1710110).

References

- Y. Song, E. Ozdemir, S. Ramesh, A. Adishev, S. Subramanian, A. Harale, M. Albuali, B. A. Fadhel, A. Jamal, D. Moon, S. H. Choi and C. T. Yavuz, *Science*, 2020, **367**, 777–781.
- J. Tollefson, *Nature*, 2017, **551**, 283–283.
- X. Jiang, Y. Jiao, C. Moran, X. W. Nie, Y. T. Gong, X. W. Guo, K. S. Walton and C. S. Song, *Catal. Commun.*, 2019, **118**, 10–14.
- C. Figueres, C. Le Quéré, A. Mahindra, O. Bäte, G. Whiteman, G. Peters and D. Guan, *Nature*, 2018, **564**, 27–30.
- Q. Li, Y. Ouyang, H. Li, L. Wang and J. Zeng, *Angew. Chem., Int. Ed.*, 2022, **61**, e202108069.
- D. T. Shindell, G. Faluvegi, D. M. Koch, G. A. Schmidt, N. Unger and S. E. Bauer, *Science*, 2009, **326**, 716–718.
- C. B. Field and K. J. Mach, *Science*, 2017, **356**, 706–707.
- C. D. Elvidge, M. D. Bazilian, M. Zhizhin, T. Ghosh, K. Baugh and F. C. Hsu, *Energy Strat. Rev.*, 2018, **20**, 156–162.
- L. He, Y. L. Fan, J. Bellettre, J. Yue and L. G. Luo, *Renewable Sustainable Energy Rev.*, 2020, **119**, 109589.
- K. H. Lim, Y. F. Yue, Bella, X. Y. Gao, T. X. Zhang, F. Y. Hu, S. Das and S. Kawi, *ACS Sustainable Chem. Eng.*, 2023, **11**, 4903–4933.
- S. M. Sajjadi, M. Haghghi, F. Rahmani and J. Eshghi, *J. CO2 Util.*, 2022, **61**, 102037.
- J. Meng, T. Gu, W. Pan, C. Bu, J. Zhang, X. Wang, C. Liu, H. Xie and G. Piao, *Fuel*, 2022, **310**, 122363.
- I. V. Yentekakis, P. Panagiotopoulou and G. Artemakis, *Appl. Catal., B*, 2021, **296**, 120210.
- J. Rockström, O. Gaffney, J. Rogelj, M. Meinshausen, N. Nakicenovic and H. J. Schellnhuber, *Science*, 2017, **355**, 1269–1271.
- S. Kim, *PhD thesis*, University of California, Irvine, 2021.
- L. N. Chen, Z. G. Song, S. C. Zhang, C. K. Chang, Y. C. Chuang, X. X. Peng, C. Dun, J. J. Urban, J. H. Guo, J. L. Chen, D. Prendergast, M. Salmeron, G. A. Somorjai and J. Su, *Science*, 2023, **381**, 857–861.
- S. Bin, S. Zheyi, Z. Yun, P. Fenghongkang, Z. Kaiqing, H. Jun and L. Honglai, *Huagong Jinzhan*, 2022, **41**, 1136–1151.
- Y. B. Li, L. Zeng, G. Pang, X. E. Wei, M. H. Wang, K. Cheng, J. C. Kang, J. M. Serra, Q. H. Zhang and Y. Wang, *Appl. Catal., B*, 2023, **324**, 122299.
- R. Stevenson, *Integr. Environ. Assess. Manage.*, 2021, **17**, 488–489.
- Z. L. Ou, Z. H. Zhang, C. L. Qin, H. Q. Xia, T. Deng, J. T. Niu, J. Y. Ran and C. F. Wu, *Sustainable Energy Fuels*, 2021, **5**, 1845–1856.



21 K. M. G. Langie, K. Tak, C. Kim, H. W. Lee, K. Park, D. Kim, W. Jung, C. W. Lee, H. S. Oh, D. K. Lee, J. H. Koh, B. K. Min, D. H. Won and U. Lee, *Nat. Commun.*, 2022, **13**, 7482.

22 Z. Qin, J. Chen, X. Xie, X. Luo, T. Su and H. Ji, *Environ. Chem. Lett.*, 2020, **18**, 997–1017.

23 D. Pakhare and J. Spivey, *Chem. Soc. Rev.*, 2014, **43**, 7813–7837.

24 S. Kawi, Y. Kathiraser, J. Ni, U. Oemar, Z. Li and E. T. Saw, *ChemSusChem*, 2015, **8**, 3556–3575.

25 L. Baharudin, N. Rahmat, N. H. Othman, N. L. Shah and S. S. A. Syed-Hassan, *J. CO₂ Util.*, 2022, **61**, 102050.

26 O. Daoura, M.-N. Kaydouh, N. El-Hassan, P. Massiani, F. Launay and M. Boutros, *J. CO₂ Util.*, 2018, **24**, 112–119.

27 Z. Lv, S. Chen, X. Huang and C. Qin, *Curr. Opin. Green Sustainable Chem.*, 2023, **40**, 100771.

28 Y. Ren, Y.-Y. Ma, W.-L. Mo, J. Guo, Q. Liu, X. Fan and S.-P. Zhang, *Catalysts*, 2023, **13**, 647.

29 N. A. K. Aramouni, J. G. Touma, B. A. Tarboush, J. Zeaiter and M. N. Ahmad, *Renewable Sustainable Energy Rev.*, 2018, **82**, 2570–2585.

30 A. M. Alhassan, I. Hussain, O. A. Taialla, M. M. Awad, A. Tanimu, K. Alhooshani and S. A. Ganiyu, *J. Cleaner Prod.*, 2023, **423**, 138638.

31 K. Tomishige, D. L. Li, M. Tamura and Y. Nakagawa, *Catal. Sci. Technol.*, 2017, **7**, 3952–3979.

32 W. J. Jang, D. W. Jeong, J. O. Shim, H. M. Kim, H. S. Roh, I. H. Son and S. J. Lee, *Appl. Energy*, 2016, **173**, 80–91.

33 B. Yuan, T. Zhu, Y. W. Han, X. L. Zhang, M. D. Wang and C. Li, *Atmosphere*, 2023, **14**, 770.

34 M. Z. Ouyang, P. Boldrin, R. C. Maher, X. L. Chen, X. H. Liu, L. F. Cohen and N. P. Brandon, *Appl. Catal.*, **B**, 2019, **248**, 332–340.

35 M. K. Nikoo and N. A. S. Amin, *Fuel Process. Technol.*, 2011, **92**, 678–691.

36 A. M. Gadalla and B. Bower, *Chem. Eng. Sci.*, 1988, **43**, 3049–3062.

37 R. Mansoor and M. Tahir, *Energy Fuels*, 2021, **35**, 3675–3714.

38 Z. Wu, B. Yang, S. Miao, W. Liu, J. Xie, S. Lee, M. J. Pellin, D. Xiao, D. Su and D. Ma, *ACS Catal.*, 2019, **9**, 2693–2700.

39 A. L. A. Marinho, F. S. Toniolo, F. B. Noronha, F. Epron, D. Duprez and N. Bion, *Appl. Catal.*, **B**, 2021, **281**, 119459.

40 M. A. Vasiliades, C. M. Damaskinos, P. Djinović, A. Pintar and A. M. Efstratiou, *Catal. Commun.*, 2021, **149**, 106237.

41 S. Kim, J. Lauterbach and E. Sasmaz, *ACS Catal.*, 2021, **11**, 8247–8260.

42 C. C. Chong, Y. W. Cheng, M. B. Bahari, L. P. Teh, S. Z. Abidin and H. D. Setiabudi, *Int. J. Hydrogen Energy*, 2021, **46**, 24687–24708.

43 A. S. Al-Fatesh, N. Patel, A. H. Fakirah, M. F. Alotibi, S. B. Alreshaidan and R. Kumar, *Catal. Rev.: Sci. Eng.*, 2023, 1–99, DOI: [10.1080/01614940.2023.2211447](https://doi.org/10.1080/01614940.2023.2211447).

44 N. A. K. Aramouni, J. G. Touma, B. Abu Tarboush, J. Zeaiter and M. N. Ahmad, *Renewable Sustainable Energy Rev.*, 2018, **82**, 2570–2585.

45 B. Shao, Z. Q. Wang, X. Q. Gong, H. L. Liu, F. Qian, P. Hu and J. Hu, *Nat. Commun.*, 2023, **14**, 996.

46 P. Yin, S. L. Hu, K. Qian, Z. Y. Wei, L. L. Zhang, Y. Lin, W. X. Huang, H. F. Xiong, W. X. Li and H. W. Liang, *Nat. Commun.*, 2021, **12**, 4865.

47 F. Behafarid and B. Roldan Cuenya, *Top. Catal.*, 2013, **56**, 1542–1559.

48 O. Daoura, G. Fornasieri, M. Boutros, N. El Hassan, P. Beaunier, C. Thomas, M. Selmane, A. Miche, C. Sassoye, O. Ersen, W. Baaziz, P. Massiani, A. Bleuzen and F. Launay, *Appl. Catal.*, **B**, 2021, **280**, 119417.

49 X. Chen, L. Yin, K. Long, H. Sun, M. Sun, H. Wang, Q. Zhang and P. Ning, *J. Energy Inst.*, 2020, **93**, 2255–2263.

50 R. H. Ouyang, J. X. Liu and W. X. Li, *J. Am. Chem. Soc.*, 2013, **135**, 1760–1771.

51 W. Liu, L. Li, X. Zhang, Z. Wang, X. Wang and H. Peng, *J. CO₂ Util.*, 2018, **27**, 297–307.

52 H. Peng, X. Zhang, L. Zhang, C. Rao, J. Lian, W. Liu, J. Ying, G. Zhang, Z. Wang, N. Zhang and X. Wang, *ChemCatChem*, 2017, **9**, 127–136.

53 N. Gao, M. Cheng, C. Quan and Y. Zheng, *Fuel*, 2020, **273**, 117702.

54 Q. Liu, P. Rzepka, H. Frey, J. Tripp, A. Beck, L. Artiglia, M. Ranocchiari and J. A. van Bokhoven, *Mater. Today Nano*, 2022, **20**, 100273.

55 T. W. Hansen, A. T. Delariva, S. R. Challa and A. K. Datye, *Acc. Chem. Res.*, 2013, **46**, 1720–1730.

56 J. W. Han, J. S. Park, M. S. Choi and H. Lee, *Appl. Catal.*, **B**, 2017, **203**, 625–632.

57 S. B. Kim, A. A. S. Eissa, M. J. Kim, E. S. Goda, J. R. Youn and K. Lee, *Catalysts*, 2022, **12**, 423.

58 Z. Z. Qin, J. Chen, X. L. Xie, X. Luo, T. M. Su and H. B. Ji, *Environ. Chem. Lett.*, 2020, **18**, 997–1017.

59 Z. R. Xiao, F. Hou, J. J. Zhang, Q. C. Zheng, J. S. Xu, L. Pan, L. Wang, J. J. Zou, X. W. Zhang and G. Z. Li, *ACS Appl. Mater. Interfaces*, 2021, **13**, 48838–48854.

60 J. Á. E. L. Bomfim, J. F. S. C. Filho, T. D. Bezerra, F. C. Rangel, T. A. Simões, P. N. Romano and R. S. da Cruz, in *Heterogeneous Catalysis*, 2022, pp. 175–206, DOI: [10.1016/b978-0-323-85612-6.00007-3](https://doi.org/10.1016/b978-0-323-85612-6.00007-3).

61 B. Yuan, T. Zhu, Y. Han, X. Zhang, M. Wang and C. Li, *Atmosphere*, 2023, **14**, 770.

62 J. M. Ginsburg, J. Pina, T. El Solh and H. I. de Lasa, *Ind. Eng. Chem. Res.*, 2005, **44**, 4846–4854.

63 L. Huang, D. Li, D. Tian, L. Jiang, Z. Li, H. Wang and K. Li, *Energy Fuels*, 2022, **36**, 5102–5151.

64 S. Helveg, J. Sehested and J. R. Rostrup-Nielsen, *Catal. Today*, 2011, **178**, 42–46.

65 X. Li, D. Li, H. Tian, L. Zeng, Z.-J. Zhao and J. Gong, *Appl. Catal.*, **B**, 2017, **202**, 683–694.

66 D. D. Gong, S. S. Li, S. X. Guo, H. G. Tang, H. Wang and Y. Liu, *Appl. Surf. Sci.*, 2018, **434**, 351–364.

67 X. H. Zhao, B. Joseph, J. Kuhn and S. Ozcan, *iScience*, 2020, **23**, 101082.

68 Q. L. Yang, G. L. Liu and Y. Liu, *Ind. Eng. Chem. Res.*, 2018, **57**, 1–17.

69 A. S. Al-Fatesh, H. Atia, J. K. Abu-Dahrieh, A. A. Ibrahim, R. Eckelt, U. Armbruster, A. E. Abasaeed and



A. H. Fakieha, *Int. J. Hydrogen Energy*, 2019, **44**, 20770–20781.

70 C. T. Kresge, M. E. Leonowicz, W. J. Roth, J. C. Vartuli and J. S. Beck, *Nature*, 1992, **359**, 710–712.

71 S. A. Theofanidis, V. V. Galvita, H. Poelman and G. B. Marin, *ACS Catal.*, 2015, **5**, 3028–3039.

72 X. Y. Gao, J. Y. Li, M. D. Zheng, S. Y. Cai, J. Y. Zhang, S. Askari, N. Dewangan, J. Ashok and S. Kawi, *Process Saf. Environ. Prot.*, 2021, **156**, 598–616.

73 Q. L. M. Ha, U. Armbruster, H. Atia, M. Schneider, H. Lund, G. Agostini, J. Radnik, H. T. Vuong and A. Martin, *Catalysts*, 2017, **7**, 157.

74 J. Artz, T. E. Müller, K. Thenert, J. Kleinekorte, R. Meys, A. Sternberg, A. Bardow and W. Leitner, *Chem. Rev.*, 2018, **118**, 434–504.

75 J. Juan-Juan, M. C. Román-Martínez and M. J. Illán-Gómez, *Appl. Catal., A*, 2009, **355**, 27–32.

76 W. Y. Kim, Y. H. Lee, H. Park, Y. H. Choi, M. H. Lee and J. S. Lee, *Catal. Sci. Technol.*, 2016, **6**, 2060–2064.

77 J.-K. Xu, Z.-J. Li, J.-H. Wang, W. Zhou and J.-X. Ma, *Acta Phys.-Chim. Sin.*, 2009, **25**, 253–260.

78 X. Y. Gao, K. Hidajat and S. Kawi, *J. CO₂ Util.*, 2016, **15**, 146–153.

79 W. F. Monteiro, M. O. Vieira, C. O. Calgaro, O. W. Perez-Lopez and R. A. Ligabue, *Fuel*, 2019, **253**, 713–721.

80 S. C. Tian, F. Yan, Z. T. Zhang and J. G. Jiang, *Sci. Adv.*, 2019, **5**, eaav5077.

81 B. Shao, Z. Q. Wang, X. Q. Gong, H. Liu, F. Qian, P. Hu and J. Hu, *Nat. Commun.*, 2023, **14**, 996.

82 J. Meng, W. Pan, T. Gu, C. Bu, J. Zhang, X. Wang, C. Liu, H. Xie and G. Piao, *Energy Fuels*, 2021, **35**, 19568–19580.

83 T. S. Phan, A. R. Sane, B. R. de Vasconcelos, A. Nzihou, P. Sharrock, D. Grouset and D. P. Minh, *Appl. Catal., B*, 2018, **224**, 310–321.

84 J. Wu, L.-Y. Qiao, Z.-F. Zhou, G.-J. Cui, S.-S. Zong, D.-J. Xu, R.-P. Ye, R.-P. Chen, R. Si and Y.-G. Yao, *ACS Catal.*, 2018, **9**, 932–945.

85 H. B. Kim and E. D. Park, *Catal. Today*, 2023, **411–412**, 113817.

86 P. Lu, Q. X. Huang, Y. Chi and J. H. Yan, *Energy Fuels*, 2017, **31**, 8283–8290.

87 C. F. Lv, L. L. Xu, M. D. Chen, Y. Cui, X. Y. Wen, Y. P. Li, C. E. Wu, B. Yang, Z. C. Miao, X. Hu and Q. H. Shou, *Front. Chem.*, 2020, **8**, 269.

88 S. Boujday, J. F. Lambert and M. Che, *ChemPhysChem*, 2004, **5**, 1003–1013.

89 O. Daoura, G. Fornasieri, M. Boutros, N. El Hassan, P. Beaunier, C. Thomas, M. Selmane, A. Miche, C. Sassoye, O. Ersen, W. Baaziz, P. Massiani, A. Bleuzen and F. Launay, *Appl. Catal., B*, 2021, **280**, 119417.

90 P. Schmidt-Winkel, W. W. Lukens, D. Y. Zhao, P. D. Yang, B. F. Chmelka and G. D. Stucky, *J. Am. Chem. Soc.*, 1999, **121**, 254–255.

91 V. Meynen, P. Cool and E. F. Vansant, *Microporous Mesoporous Mater.*, 2009, **125**, 170–223.

92 A. M. Ranjekar and G. D. Yadav, *J. Indian Chem. Soc.*, 2021, **98**, 100002.

93 B. Erjavec, R. Kaplan and A. Pintar, *Catal. Today*, 2015, **241**, 15–24.

94 J. Ni, L. W. Chen, J. Y. Lin and S. Kawi, *Nano Energy*, 2012, **1**, 674–686.

95 A. Abdulrasheed, A. A. Jalil, Y. Gambo, M. Ibrahim, H. U. Hambali and M. Y. S. Hamill, *Renewable Sustainable Energy Rev.*, 2019, **108**, 175–193.

96 Y. J. Chai, Y. Fu, H. Feng, W. B. Kong, C. K. Yuan, B. R. Pan, J. Zhang and Y. H. Sun, *ChemCatChem*, 2018, **10**, 2078–2086.

97 O. Alioui, M. Badawi, A. Erto, M. A. Amin, V. Tirth, B.-H. Jeon, S. Islam, M. Balsamo, M. Virginie, B. Ernst and Y. Benguerba, *Catal. Rev.: Sci. Eng.*, 2022, **65**, 1468–1520.

98 X. Y. Li, D. Li, H. Tian, L. Zeng, Z. J. Zhao and J. L. Gong, *Appl. Catal., B*, 2017, **202**, 683–694.

99 X. D. Li, Y. L. Huang, Q. Zhang, C. H. Luan, V. A. Vinokurov and W. Huang, *Energy Convers. Manage.*, 2019, **179**, 166–177.

100 Y. Y. Zhan, K. Song, Z. M. Shi, C. S. Wan, J. H. Pan, D. L. Li, C. Au and L. L. Jiang, *Int. J. Hydrogen Energy*, 2020, **45**, 2794–2807.

101 X. D. Li, Y. L. Huang, Q. Zhang, Z. J. Zuo, X. D. Wang, V. A. Vinokurov, Z. Wang and W. Huang, *Fuel*, 2019, **254**, 115562.

102 Y. H. Wang, H. M. Liu and B. Q. Xu, *J. Mol. Catal. A: Chem.*, 2009, **299**, 44–52.

103 J. Yu, X. Wu, X. Liu, Y. Guo, J. Chu, P. Huang, J. Wu, J. Fu, Z. Wang, C. Zhao and J. Liu, *Energy Fuels*, 2023, **37**, 16672–16687.

104 T. Setia Febriatna, P. Setyo Darmanto and F. Bagja Juangsa, *Clean Energy*, 2023, **7**, 313–327.

105 I. S. Omodolor, H. O. Otor, J. A. Andonegui, B. J. Allen and A. C. Alba-Rubio, *Ind. Eng. Chem. Res.*, 2020, **59**, 17612–17631.

106 J. I. Huertas, M. D. Gomez, N. Giraldo and J. Garzón, *J. Chem.*, 2015, **2015**, 1–7.

107 J. Chen, L. Duan, Y. Ma, Y. Jiang, A. Huang, H. Zhu, H. Jiao, M. Li, Y. Hu, H. Zhou, Y. Xu, F. Donat, M. Awais Naeem and O. Kröcher, *Fuel*, 2023, **334**, 126630.

108 Q. Chen, J. Zhang, B. Pan, W. Kong, Y. Chen, W. Zhang and Y. Sun, *Chem. Eng. J.*, 2017, **320**, 63–73.

109 J. G. Meng, T. T. Gu, W. Pan, C. S. Bu, J. B. Zhang, X. Y. Wang, C. Q. Liu, H. Xie and G. L. Piao, *Fuel*, 2022, **310**, 122363.

110 J. M. Tang, J. G. Meng, W. Pan, T. T. Gu, Q. Zhang, J. B. Zhang, X. Y. Wang, C. S. Bu and G. L. Piao, *Int. J. Hydrogen Energy*, 2023, **48**, 19033–19045.

111 L. Wang and F. Wang, *Energy Fuels*, 2022, **36**, 5594–5621.

112 A. A. Ibrahim, A. S. Al-Fatesh, N. S. Kumar, A. E. Abasaed, S. O. Kasim and A. H. Fakieha, *Catalysts*, 2020, **10**, 242.

113 G. J. Zhang, J. W. Liu, Y. Xu and Y. H. Sun, *Int. J. Hydrogen Energy*, 2018, **43**, 15030–15054.

114 J. Zhang, H. Wang and A. K. Dalai, *Appl. Catal., A*, 2008, **339**, 121–129.

115 A. Beheshti Askari, M. Al Samarai, B. Morana, L. Tillmann, N. Pfander, A. Wandzilak, B. Watts, R. Belkhou, M. Muhler and S. DeBeer, *ACS Catal.*, 2020, **10**, 6223–6230.



116 M. N. Kaydouh, N. El Hassan, A. Davidson, S. Casale, H. El Zakhem and P. Massiani, *Microporous Mesoporous Mater.*, 2016, **220**, 99–109.

117 B. Li, L. Li, K. Tomishige and X. Wang, *Int. J. Hydrogen Energy*, 2022, **47**, 37792–37810.

118 N. D. Charisiou, L. Tzounis, V. Sebastian, S. J. Hinder, M. A. Baker, K. Polychronopoulou and M. A. Goula, *Appl. Surf. Sci.*, 2019, **474**, 42–56.

119 Z. W. Li, Y. Kathiraser, J. Ashok, U. Oemar and S. Kawi, *Langmuir*, 2014, **30**, 14694–14705.

120 L. V. Mattos, G. Jacobs, B. H. Davis and F. B. Noronha, *Chem. Rev.*, 2012, **112**, 4094–4123.

121 H. R. Gurav, S. Dama, V. Samuel and S. Chilukuri, *J. CO2 Util.*, 2017, **20**, 357–367.

122 B. Li, X. Q. Yuan, L. Y. Li, B. T. Li, X. J. Wang and K. Tomishige, *Int. J. Hydrogen Energy*, 2021, **46**, 31608–31622.

123 A. S. Al-Fatesh, A. Hanan, A. A. Ibrahim, A. H. Fakieha, S. K. Singh, N. K. Labhsetwar, H. Shaikh and S. O. Qasim, *Renewable Energy*, 2019, **140**, 658–667.

124 J. T. Niu, F. Guo, J. Y. Ran, W. J. Qi and Z. Q. Yang, *Int. J. Hydrogen Energy*, 2020, **45**, 30267–30287.

125 X. Zhang, J. Deng, M. Pupucevski, S. Impeng, B. Yang, G. Chen, S. Kuboon, Q. Zhong, K. Faungnawakij, L. Zheng, G. Wu and D. Zhang, *ACS Catal.*, 2021, **11**, 12087–12095.

126 K. H. Oh, J. H. Lee, K. Kim, H.-K. Lee, S. W. Kang, J.-I. Yang, J.-H. Park, C. S. Hong, B.-H. Kim and J. C. Park, *J. Mater. Chem. A*, 2023, **11**, 1666–1675.

127 T. T. Zhang, Z. X. Liu, Y. A. Zhu, Z. C. Liu, Z. J. Sui, K. K. Zhu and X. G. Zhou, *Appl. Catal., B*, 2020, **264**, 118497.

128 M. A. Vasiliades, C. M. Damaskinos, K. K. Kyprianou, M. Kollia and A. M. Efstatiou, *Catal. Today*, 2020, **355**, 788–803.

129 B. Li, T. Li, Y. S. Xiao and Z. W. Liu, *J. Rare Earths*, 2023, **41**, 830–838.

130 S. M. Kim, P. M. Abdala, T. Margossian, D. Hosseini, L. Foppa, A. Armutlulu, W. van Beek, A. Comas-Vives, C. Coperet and C. Muller, *J. Am. Chem. Soc.*, 2017, **139**, 1937–1949.

131 R. G. Zhang, X. Q. Guo, B. J. Wang and L. M. Ling, *J. Phys. Chem. C*, 2015, **119**, 14135–14144.

132 M. Gerosa, C. E. Bottani, L. Caramella, G. Onida, C. Di Valentini and G. Pacchioni, *J. Chem. Phys.*, 2015, **143**, 134702.

133 Y. X. Dai, R. Zou, T. E. Ba, J. Zhang and C. J. Liu, *J. CO2 Util.*, 2021, **51**, 101647.

134 F. Menegazzo, C. Pizzolitto, E. Ghedini, A. Di Michele, G. Cruciani and M. Signoretto, *C*, 2018, **4**, 60.

135 M. Ouyang, P. Boldrin, R. C. Maher, X. Chen, X. Liu, L. F. Cohen and N. P. Brandon, *Appl. Catal., B*, 2019, **248**, 332–340.

136 Z. Wang, X. Shao, A. Larcher, K. Xie, D. Dong and C.-Z. Li, *Catal. Today*, 2013, **216**, 44–49.

137 Z. Sun, C. K. Russell, K. J. Whitty, E. G. Eddings, J. Z. Dai, Y. L. Zhang, M. H. Fan and Z. Q. Sun, *Prog. Energy Combust. Sci.*, 2023, **96**, 101045.

138 S. Joo, A. Seong, O. Kwon, K. Kim, J. H. Lee, R. J. Gorte, J. M. Vohs, J. W. Han and G. Kim, *Sci. Adv.*, 2020, **6**, eabb1573.

139 E. G. Mahoney, J. M. Pusel, S. M. Stagg-Williams and S. Faraji, *J. CO2 Util.*, 2014, **6**, 40–44.

140 H. Ay and D. Üner, *Appl. Catal., B*, 2015, **179**, 128–138.

141 S. Q. Gao, Y. A. Li, W. Z. Guo, X. Ding, L. Zheng, L. Wu, H. L. Yan and Y. Q. Wang, *Mol. Catal.*, 2022, **533**, 112766.

142 M. Zhang, J. F. Zhang, Y. Q. Wu, J. X. Pan, Q. D. Zhang, Y. S. Tan and Y. Z. Han, *Appl. Catal., B*, 2019, **244**, 427–437.

143 D. P. Liu, X. Y. Quek, W. N. E. Cheo, R. Lau, A. Borgna and Y. H. Yang, *J. Catal.*, 2009, **266**, 380–390.

144 Y. Lou, M. Steib, Q. Zhang, K. Tiefenbacher, A. Horváth, A. Jentys, Y. Liu and J. A. Lercher, *J. Catal.*, 2017, **356**, 147–156.

145 J. W. Hu, V. V. Galvita, H. Poelman, C. Detavernier and G. B. Marin, *Appl. Catal., B*, 2018, **231**, 123–136.

146 M. Zhang, J. Zhang, Y. Wu, J. Pan, Q. Zhang, Y. Tan and Y. Han, *Appl. Catal., B*, 2019, **244**, 427–437.

147 Y. Z. Ge, Y. J. Ma, R. X. Xue, F. W. Wang, P. Su, Z. J. Wang and Y. S. Li, *ACS Omega*, 2021, **6**, 17019–17026.

148 N. Wang, K. Shen, L. H. Huang, X. P. Yu, W. Z. Qian and W. Chu, *ACS Catal.*, 2013, **3**, 1638–1651.

149 T. Herminio, M. R. Cesário, V. D. Silva, T. A. Simões, E. S. Medeiros, D. A. Macedo, H. L. Tidahy, C. Gennequin and E. Abi-Aad, *Environ. Chem. Lett.*, 2020, **18**, 895–903.

150 K.-W. Jeon, H.-M. Kim, B.-J. Kim, Y.-L. Lee, H.-S. Na, J.-O. Shim, W.-J. Jang and H.-S. Roh, *Fuel Process. Technol.*, 2021, **219**, 106877.

151 M. Akri, S. Zhao, X. Li, K. Zang, A. F. Lee, M. A. Isaacs, W. Xi, Y. Gangarajula, J. Luo, Y. Ren, Y. T. Cui, L. Li, Y. Su, X. Pan, W. Wen, Y. Pan, K. Wilson, L. Li, B. Qiao, H. Ishii, Y. F. Liao, A. Wang, X. Wang and T. Zhang, *Nat. Commun.*, 2019, **10**, 5181.

152 W. Mui, *PhD*, California Institute of Technology, 2017.

153 O. U. Osazuwa, S. Z. Abidin, X. Fan, A. N. Amenaghawon and M. T. Azizan, *J. Environ. Chem. Eng.*, 2021, **9**, 105052.

154 S. S. Mabaleha, F. Gholizadeh and P. Kalita, *Mol. Catal.*, 2023, **547**, 113398.

155 J.-C. Seo, H. Kim, Y.-L. Lee, S. Nam, H.-S. Roh, K. Lee and S. B. Park, *ACS Sustainable Chem. Eng.*, 2021, **9**, 894–904.

156 X. Fang, C. Peng, H. Peng, W. Liu, X. Xu, X. Wang, C. Li and W. Zhou, *ChemCatChem*, 2015, **7**, 3753–3762.

157 N. Wang, Z. X. Xu, J. Deng, K. Shen, X. P. Yu, W. Z. Qian, W. Chu and F. Wei, *ChemCatChem*, 2014, **6**, 1470–1480.

158 J. Tian, B. Ma, S. Bu, Q. Yuan and C. Zhao, *Chem. Commun.*, 2018, **54**, 13993–13996.

159 M. Wang, Q. Zhang, T. Zhang, Y. Wang, J. Wang, K. Long, Z. Song, X. Liu and P. Ning, *Chem. Eng. J.*, 2017, **313**, 1370–1381.

160 A. S. Al-Fatesh, J. Khatri, R. Kumar, V. K. Srivastava, A. I. Osman, T. S. AlGarni, A. A. Ibrahim, A. E. Abasaeed, A. H. Fakieha and D. W. Rooney, *Energy Sci. Eng.*, 2022, **10**, 866–880.



161 C. Sanchez, C. Boissiere, D. Gross, C. Laberty and L. Nicole, *Chem. Mater.*, 2008, **20**, 682–737.

162 Q. Ma, L. Guo, Y. Fang, H. Li, J. Zhang, T.-S. Zhao, G. Yang, Y. Yoneyama and N. Tsubaki, *Fuel Process. Technol.*, 2019, **188**, 98–104.

163 S. M. Sajjadi and M. Haghghi, *Chem. Eng. J.*, 2019, **362**, 767–782.

164 S. M. Sajjadi, M. Haghghi and F. Rahmani, *J. Nat. Gas Sci. Eng.*, 2015, **22**, 9–21.

165 S. J. Hassani Rad, M. Haghghi, A. Alizadeh Eslami, F. Rahmani and N. Rahemi, *Int. J. Hydrogen Energy*, 2016, **41**, 5335–5350.

166 S. Aghamohammadi, M. Haghghi, M. Maleki and N. Rahemi, *Mol. Catal.*, 2017, **431**, 39–48.

167 N. Yahi, S. Menad and I. Rodriguez-Ramos, *Green Processes Synth.*, 2015, **4**, 479–486.

168 A. L. A. Marinho, R. C. Rabelo-Neto, F. Epron, N. Bion, F. S. Toniolo and F. B. Noronha, *Appl. Catal., B*, 2020, **268**, 118387.

