

# Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

## Film-through large perovskite grains formation via a combination of sequential thermal and solvent treatment †

Fan Zhang,<sup>‡ab</sup> Jun Song,<sup>‡a</sup> Linxing Zhang,<sup>a</sup> Fangfang Niu,<sup>a</sup> Yuying Hao,<sup>b</sup> Pengju Zeng,<sup>a</sup> Hanben Niu<sup>\*ab</sup>, Jinsong Huang<sup>c</sup> and Jiarong Lian<sup>‡\*a</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Organic–inorganic halide perovskites have recently attracted strong research interest for the fabrication of high-performance, low-cost photovoltaic devices. Recently, we reported a highly reproducible procedure to fabricate high-performance organic–inorganic halide perovskite solar cells. This procedure, based on a one-step, solvent-induced, fast deposition-crystallization method, involves the use of sec-butyl alcohol as a new solvent to induce the  $\text{CH}_3\text{NH}_3\text{PbI}_3$  fast crystallization deposition. In the present study, we propose a reproducible fabrication method to prepare both flat and large-grain perovskite film by adding a pre-annealing step to strengthen the perovskite nucleation, aiming to facilitate the excess  $\text{CH}_3\text{NH}_3\text{I}$  and solvent remove in sec-butyl alcohol soaking process, in which all films with thickness between 420 nm and 1  $\mu\text{m}$  performed uniform and film-through grains. The best performing planar device obtained with this procedure had an efficiency of 17.2% under AM 1.5G illumination and an average power conversion efficiency of  $16.2 \pm 0.5\%$ . We also analyzed the efficiency of halide perovskite planar solar cells as a function of the perovskite film thickness; the efficiency dropped only slightly to 15.7% when the perovskite film thickness was increased to 1  $\mu\text{m}$ .

### Introduction

Organic–inorganic halide perovskites have recently attracted strong research interest owing to their excellent optical, electronic, and material properties such as high absorption coefficient, high open-circuit voltage ( $V_{\text{OC}}$ ) by small exciton binding energy, long charge carrier diffusion length by formation of shallow traps, and low temperature solution processibility.<sup>1–8</sup> Since the first report of perovskite materials in photovoltaic devices, published in 2009, organometallic lead-halide perovskite solar cells have shown one of the most rapid growths ever in photovoltaic history.<sup>9–13</sup> Within a short period of time, the certified power conversion efficiency (PCE) of perovskite solar cells has already exceeded 21%.<sup>14</sup> These results suggest an enormous potential for perovskite compounds as efficient photoactive materials for photovoltaic applications.<sup>15–18</sup>

Lead-halide perovskite films can be deposited on substrates through in situ reactions of precursors via single- or two-step

methods.<sup>19–20</sup> Two types of device architectures are typically adopted in perovskite solar cells. It was initially assumed that a mesostructured (or nanostructured) matrix may be necessary for efficient charge transport and collection in perovskite solar cells.<sup>21</sup> To simplify the device architecture and processing procedures, planar architectures without mesoporous layers were proposed and proved to be very suitable for perovskite solar cells, owing to long charge diffusion lengths.<sup>22–23</sup> To avoid shunting in such planar devices, a nonporous homogenous perovskite film must be deposited. However, films produced by the conventional spin-coating methods were found to be composed of large  $\text{CH}_3\text{NH}_3\text{PbI}_3$  grains and many uncovered pin-hole areas.<sup>24</sup> Therefore, to achieve optimum film morphology, effective ways to manipulate nucleation and growth of perovskite crystals in solution-processed systems, particularly in planar systems, are highly sought after.

Recently, a new method called “solvent engineering” was proposed in one-step spin coating to fabricate perovskite layers with uniform and dense planar geometry. Jeon et al. reported that the perovskite film was deposited from a precursor solution dissolved in a mixture of dimethyl sulfoxide (DMSO) and  $\gamma$ -butyrolactone (GBL) (DMSO:GBL = 3:7 v/v), immediately followed by a toluene drip while the substrate was spinning.<sup>25</sup> Independently, Xiao et al. reported that flat and uniform perovskite thin films can be obtained by a fast deposition-crystallization (FDC) method involving spin coating from a dimethyl formamide (DMF) solution, followed by chlorobenzene (CB) dripping during the spin coating to induce crystallization.<sup>26</sup> This approach greatly resembles the solvent engineering method (DMSO/GBL/toluene) developed by Jeon

<sup>a</sup> Institute of Optoelectronics, Key Lab of Optoelectronics Devices and Systems of Ministry of Education/Guangdong Province, Shenzhen University, 518060, Shenzhen, China; and Key Laboratory of Micro-Nano Measuring and Imaging in Biomedical Optics, College of Optoelectronic Engineering, Shenzhen University, Shenzhen 518060, China. \* E-mail: [ljr@szu.edu.cn](mailto:ljr@szu.edu.cn), [niuhb@szu.edu.cn](mailto:niuhb@szu.edu.cn).

<sup>b</sup> Key Laboratory of Advanced Transducers and Intelligent Control System (Ministry of Education), Taiyuan University of Technology, Taiyuan 030024, China.

<sup>c</sup> Department of Mechanical and Materials Engineering, Nebraska Center for Materials and Nanoscience, University of Nebraska-Lincoln, Lincoln, Nebraska 68588-0656, USA.

† Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x


‡ These authors contributed equally to this work.

et al. Despite the similarity in protocols, the results are very different. The presence of DMSO, which strongly coordinates with lead halides by forming intermediate phases, prevents immediate crystallization upon toluene drip, as observed from the lack of color change in the film. On the other hand, CB drip instantly promotes darkening, which suggests instantaneous perovskite formation. These methods, based on the use of toluene or chlorobenzene, are not applicable to massive production, owing to their high toxicity and cost. Recently, we verified the validity by using sec-butyl alcohol as a new solvent both in washing step to promote fast crystallization and in soaking step to remove excessive methylammonium iodide (MAI) content in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  films.<sup>27</sup> Although good PCEs of approximately 14.3% have been achieved, they were limited by the poor quality of perovskite film when its thickness was increased.

Herein, we report an improved fabrication procedure which is applicable to fabricate perovskite films with larger thickness and superior crystal morphology. In this procedure, a thermal pre-annealing is proved to be a crucial step in improving the growth of perovskite film morphology. The best-performing planar structure device obtained with pre-annealing at 100 °C exhibited an efficiency of 17.2% under AM 1.5G illumination and an average PCE of  $16.2 \pm 0.5\%$  over 40 cells. We also examined the efficiency of halide perovskite planar-structure solar cells as a function of the thickness variation of the perovskite films, finding that the efficiency dropped only slightly to 15.7% when the perovskite film thickness was increased to about 1  $\mu\text{m}$ .

## Results and discussion

Figure 1 shows a schematic representation of the adopted fabrication process. The perovskite precursor solution was prepared by mixing 922 mg  $\text{PbI}_2$  (99.999%, Alfa Aesar) and 349.8 mg  $\text{CH}_3\text{NH}_3\text{I}$  in 0.9 mL of DMF (99.5%, Sigma-Aldrich) and 0.1 mL of DMSO (99.5%, Sigma-Aldrich), with  $\text{PbI}_2$ :  $\text{CH}_3\text{NH}_3\text{I}$  molar ratio of 1: 1.1. The mixture solution was spin coated on the poly(3,4-ethylenedioxythiophene) poly(styrenesulphonate) (PEDOT: PSS) layer at 6,000 rpm and, after 7-9 seconds of delay time depending on the concentration of the precursor solution, the wet film was washed with sec-butyl alcohol (99.5%, Sigma-Aldrich) (washing step). After sec-butyl alcohol was uniformly dropped in the center of the substrate, the perovskite film quickly changed to a dark brown color. The sec-butyl alcohol rapidly reduced the solubility of perovskite in the mixed solvent, promoting fast nucleation and crystal growth. After the spinning stopped, the film was annealed on a hot plate at 100 °C for ~30 s (defined as the pre-annealing step), quickly showing a black color with a mirror-like surface. The film was then soaked with sec-butyl alcohol for a few seconds to remove excess MAI by accurately controlling the soaking time. Subsequently, the film was dried by spinning the substrates at 6,000 rpm for 30 s and subjected to post-annealing treatment (post-annealing step). In this step, the perovskite film was transferred to the air condition in super clean room with a controlled humidity of 55%~65% for post

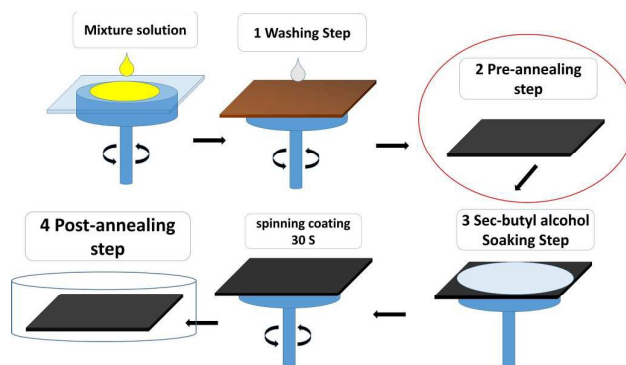


**Figure 1** Schematic illustration of the fabrication procedure including washing, pre-annealing, soaking, and post-annealing steps.

annealing process, which involves initial thermal annealing at 100 °C for 15 min and consequential solvent annealing in DMF atmosphere at 100 °C for 15 min. More descriptions on the experimental process can be found in the supporting information.

In this procedure, every step was carefully optimized to benefit the film fabrication. Excessive MAI ( $\text{PbI}_2$ : MAI= 1:1.1 molar ratio) was purposed to supplement the consumption of MAI during the sec-butyl alcohol washing and soaking steps. This is because sec-butyl alcohol washing and soaking step can remove a considerable quantity of MAI. The sec-butyl alcohol washing and soaking steps in this process promoted the formation of the crystalline perovskite film, as in our previously reported approach,<sup>27</sup> in which sec-butyl alcohol was used to induce the  $\text{CH}_3\text{NH}_3\text{PbI}_3$  fast crystallization and obtain an appropriate MAI content in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  films. It is thought that the solvent vapor in post annealing process play a key role in determining the morphology and crystallinity of perovskite film, of which an improved perovskite film can be obtained by using either of the controlled moisture<sup>32-33</sup> and DMF atmosphere<sup>28-29</sup>. So that we optimized the post-annealing process by using initial thermal annealing in air condition and consequential solvent annealing in DMF atmosphere. The pre-annealing step, which was added to our previously adopted procedure, played an important role in promoting the growth of perovskite grains.

The morphology dependence of the final perovskite films on the pre-annealing treatment was investigated by SEM. All films were prepared on ITO/PEDOT: PSS substrates to ensure identical conditions for the working device. Four representative samples obtained at different pre-annealing temperatures (w/o, 80, 100, and 120 °C) were analyzed, and their SEM images are shown in Figure 2. The top-view SEM image of the  $\text{CH}_3\text{NH}_3\text{PbI}_3$  perovskite film prepared without pre-annealing step (Figure 2a) shows a surface with fine and irregular crystallites, and the grain size was estimated to be 560 nm on average as shown in Figure S1 of the Supplementary Information. However, some voids are found at the bottom (close to the PEDOT: PSS layer) of the film from the cross-sectional SEM image of the same film in Figure 2e. When the pre-annealing temperature at 80 °C was used, the final perovskite film surface exhibited more uniform

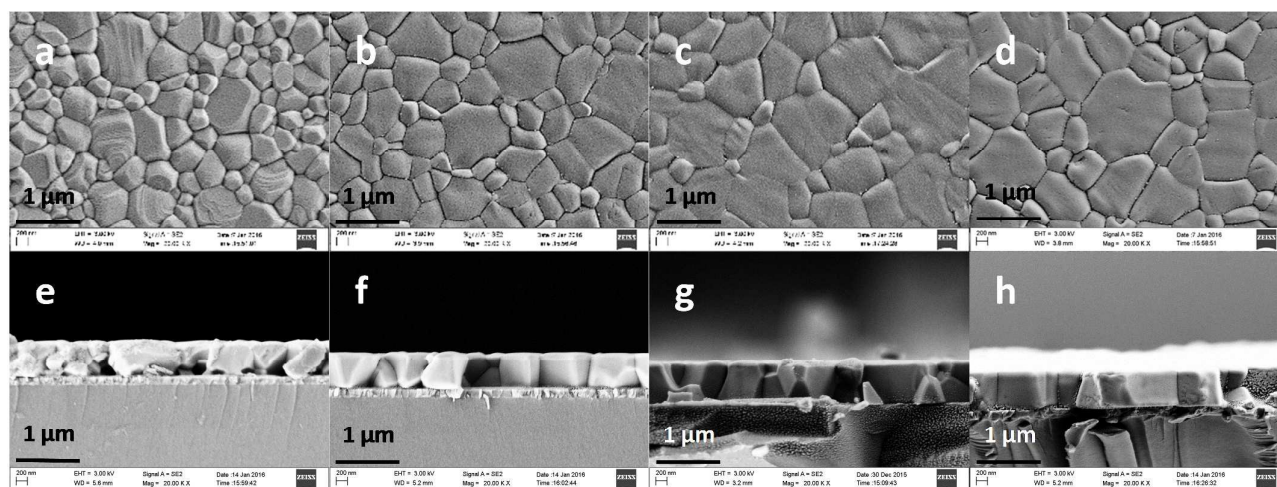


**Figure 2** Top-view (a-d) and cross-sectional (e-h) scanning electron microscopy image of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  perovskite films prepared using different pre-annealing temperatures: (a, e) without pre-annealing step, (b, f) 80 °C, (c, g) 100 °C, (d, h) 120 °C.

morphology and larger crystal grain size with an average grain size of 731.5 nm (Figure 2b). The voids are also greatly reduced and even disappeared (Figure 2f-h). The grain size of the perovskite films are even larger when continue increasing the pre-annealing temperature up to 100 °C and 120 °C, and more than 80% of the given area was occupied by 1–2  $\mu\text{m}$  large grains. It should be noted that all the films using pre-annealing step show film-through large grain distribution, which is the ideal condition for high performance PSCs because in that the charges could transport and be collected through a single grain without encountering grain boundaries and charge traps.


Photoluminescence (PL) spectra were measured to verify the composition and structure evolution of the perovskite film. An excitation light of 325 nm came into the films from the air side, and the PL signal was also collected from the air side. As shown in Figure 3a, the PL spectra of perovskite film with 100 °C-pre-annealing exhibit a PL peak at 788 nm, which is blue-shifted relative to the film without pre-annealing (794 nm). Generally, the PL emission is related to the recombination channel concerning the bandgap and trap state. The blue-shift phenomenon may imply the film with 100 °C-pre-annealing has lower trap density around the band-edge than the film without. UV-vis absorption spectra of the films with and

without pre-annealing (100 °C) are compared in Figure 3b. Note that the baselines for the UV-vis spectra without pre-annealing at long wavelengths are very high, owing to the high light scattering associated with a rough perovskite film. Compared with that of the sample without pre-annealing treatment, the absorption of the film pre-annealed at 100 °C is stronger at wavelengths in the range of 400–600 nm. The neat perovskite composition for both films of w/o and with pre-annealing treatment, can be deduced by showing sole  $\text{CH}_3\text{NH}_3\text{PbI}_3$  diffraction peaks in Figure 3c, and a slightly increased (110) orientation can also be obtained by using pre-annealing treatment.

On the basis of detailed investigation of the growth of perovskite films, a crystal growth model shown in Figure 4 was proposed. Sec-butyl alcohol rapidly reduces the solubility of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  in the mixed solvent, thereby promoting fast nucleation and crystal growth on top of the perovskite film. However, when the perovskite film is thick enough (>600 nm), the solvent and some excessive MAI may remain at the bottom of the film. It is speculated that perovskite precursor are generally colloidal dispersions in this residual solvent with a colloidal size up to the mesoscale, rather than real solutions.<sup>30</sup> The colloid is made of a soft coordination complex in the form

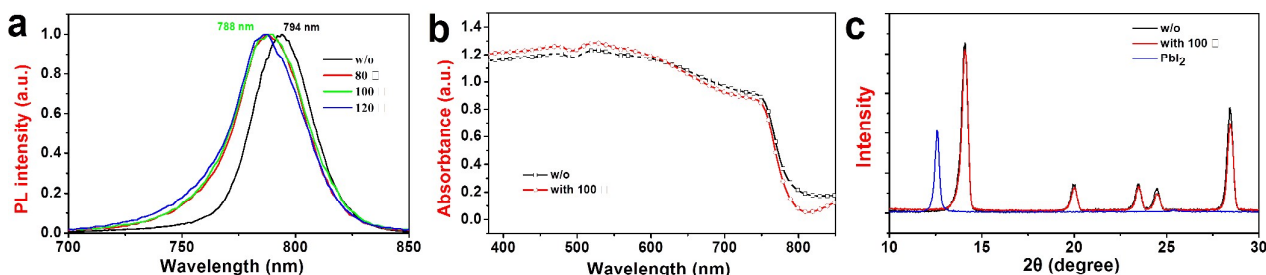

**Figure 3** (a) Normalized photoluminescence spectra (PL) of perovskite thin films prepared with different pre-annealing temperature. An excitation light of 325 nm irradiated on the film from the air side, and the PL signal was also collected from the air side. (b) Absorption spectra and (c) X-ray diffraction patterns of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  perovskite films prepared with and without pre-annealing step. The  $\text{CH}_3\text{NH}_3\text{PbI}_3$  films were spun on the surface of an ITO/PEDOT: PSS layer to ensure the identical condition to the working device.

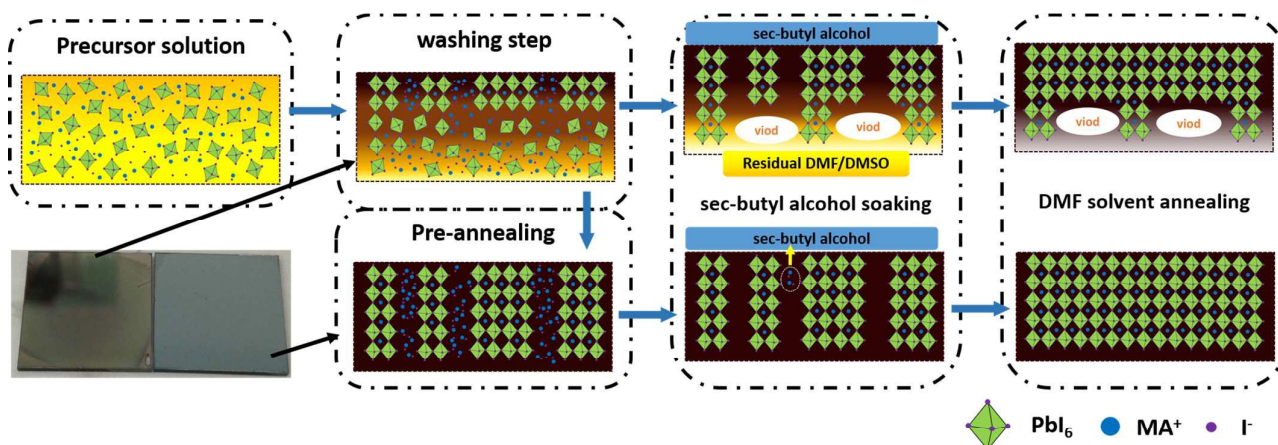

**Figure. 4** Schematic illustration of the perovskite crystal growing process, including washing, pre-annealing, soaking, and post-annealing steps.

of a lead polyhalide framework between organic and inorganic components. In the case of film w/o pre-annealing treatment, the solvent and excessive MAI underneath are more difficult to be extracted out due to their coordination in colloid structure and the limited quantity penetration of sec-butyl alcohol, therefore the undesired film morphology with voids and small grains is formed after these solvent and excessive MAI were removed in the post annealing process. Here the existence of many defects can be reflected by longer wavelength location for the PL peaks as shown in Figure 3a. when the thermal pre-annealing treatment is in use, these coordination would be interrupted due to the structure transformation from colloid to perovskite, so the enhanced sec-butyl alcohol penetration is obtained, large quantity of residual solvent and excessive MAI are extracted out in sec-butyl alcohol soaking process. Finally, the perovskite crystals and morphology grow more extensively because the employing DMF solvent annealing. Both  $\text{PbI}_2$  and  $\text{CH}_3\text{NH}_3\text{I}$  precursors are highly soluble in DMF vapor, can facilitate the diffusion and reorganization of the precursor molecules and ions.<sup>28-29</sup>


To probe the effect of the pre-annealing treatment on the photovoltaic performance, perovskite solar cells with device structure of ITO/PEDOT: PSS/ $\text{CH}_3\text{NH}_3\text{PbI}_3$ /PCBM/Bphen/Al (Figure 5), have been fabricated for comparison. Here 4,7-Diphenyl-1,10-phenanthroline (Bphen) interfacial layer with concentration of 0.7 mg/mL in ethanol is used to facilitate

electron collection and to block aluminum penetration.<sup>31</sup> Photovoltaic metrics of the PSCs using pre-annealed treatment at different temperatures are summarized in Figure 6 (a–d). Figure 6e shows the typical J–V curves for each device, and their average photovoltaic performance are also listed in Table S2. The reference devices without pre-annealing step exhibited low performances with the PCE of  $12.4 \pm 1.1\%$ ,  $V_{\text{OC}}$  of  $0.871 \pm 0.035$  V, short-circuit current density ( $J_{\text{SC}}$ ) of  $20.47 \pm 1.50$   $\text{mA}/\text{cm}^2$ , and FF of  $0.704 \pm 0.021$ , respectively. While the pre-annealing treatment is in use, all the PSCs show significantly enhanced photovoltaic performances. Taking the devices with pre-annealing temperature at  $100^\circ\text{C}$  for an example, their PCE,  $V_{\text{OC}}$ ,  $J_{\text{SC}}$ , and FF were increased to  $16.6 \pm 0.5\%$ ,  $0.972 \pm 0.008$  V,  $22.25 \pm 0.32$   $\text{mA}/\text{cm}^2$ , and  $0.766 \pm 0.007$ , respectively.


Here the increased  $J_{\text{SC}}$  can be explained by more effective carrier collection, because in that the ideal perovskite morphology with film-through large grains (seen in Figure 2), makes carriers transport and be collected through a single grain without encountering grain boundaries and charge traps. To find the origin of the enhanced  $V_{\text{OC}}$ , we compared their dark current curves of all devices, because in that  $V_{\text{OC}}$  for the given photoactive materials is determined by the equation:

$$V_{\text{OC}} = \frac{n k_B T}{q} \ln \left( \frac{J_{\text{SC}}}{J_0} \right) \quad (1)$$

Of which  $n$ ,  $k_B$ ,  $T$ ,  $q$ ,  $J_{\text{SC}}$ ,  $J_0$  stand for ideal factor, Boltzmann constant, absolute temperature, electron charge, short current

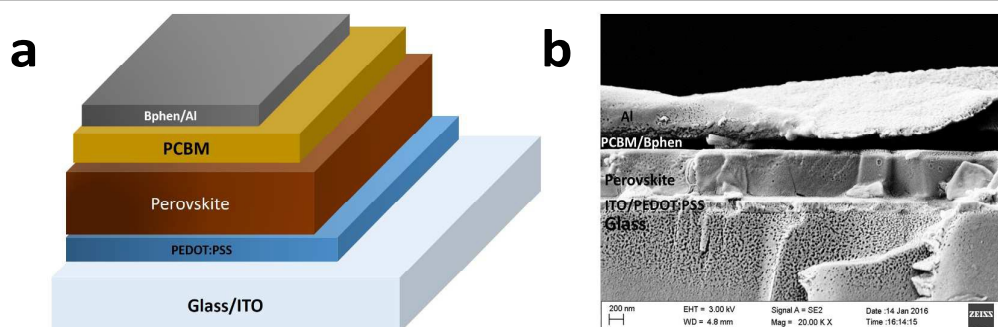

**Figure. 5** (a) Schematic device structure of perovskite solar cell; the devices were structured as ITO/PEDOT: PSS/ $\text{CH}_3\text{NH}_3\text{PbI}_3$ /PCBM/Bphen/Al. (b) Cross-sectional scanning electron microscopy image of the full perovskite solar cell under  $100^\circ\text{C}$  pre-annealing conditions.

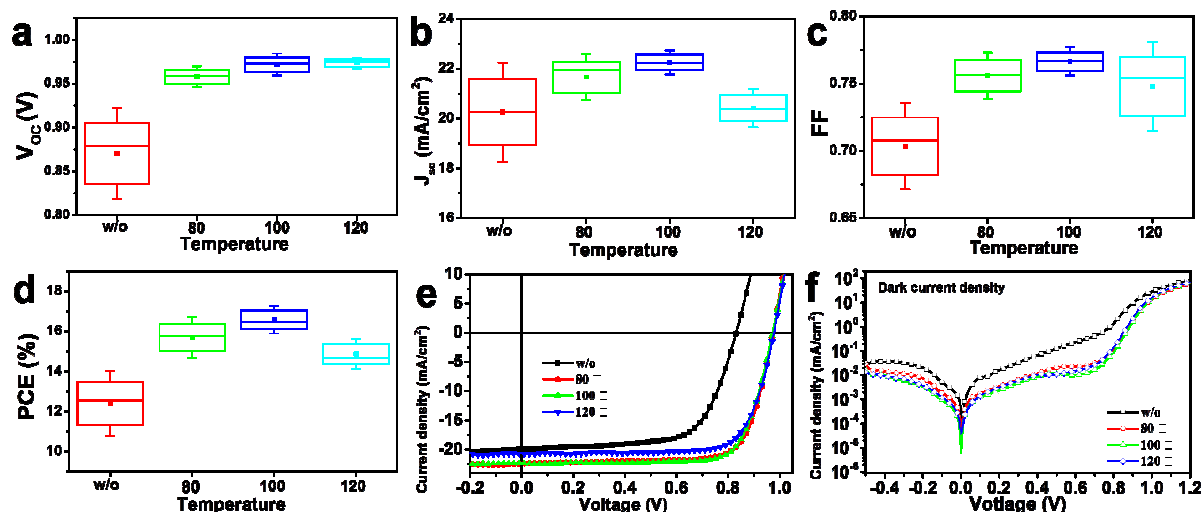

**Figure 6** Influence of pre-annealing step on the fabricated solar cells. Short-circuit current density ( $J_{sc}$ ) (a), open-circuit voltage ( $V_{oc}$ ) (b), fill factor (FF) (c), and power conversion efficiency (PCE) (d) of perovskite solar cell devices prepared at different pre-annealing temperatures of 6 cells. J-V curves of devices with different pre-annealing temperatures: (e) The J-V data were collected under AM 1.5G one sun illumination ( $100 \text{ mW/cm}^2$ ), (f) The J-V data were collected under dark.

density, and saturated reversed current density, respectively.


According to the expression of the dark current density ( $J_D$ ):

$$J_D = J_0 \left( e^{\frac{qV}{nK_B T}} - 1 \right) \quad (2)$$


As shown Figure 6f, it is easy to know that the dark current of the device was decreased about one order of magnitude when pre-annealing is in use, then lower  $J_0$  can be expected. Therefore, the obvious increased  $V_{oc}$  can be interpreted by the combination of larger  $J_{sc}$  and lower  $J_0$ .

Here the photocurrent hysteresis characteristics for all

devices have also been studied as shown in Figure S2. It is clear that the pre-annealing treatment is much effective in suppressing the undesired hysteresis phenomenon of device. For the conventional device, obvious changes from 11.0% to 12.5% in PCE, and from 0.83 V to 0.88V in  $V_{oc}$ , are found when the voltage scan direction was changed from forward to reversed one. To the contrast, we measured a 100 °C-pre-annealing device by changing the scanning directions (Figure S2c) and scanning rates (Figure S3), this photocurrent hysteresis disappeared. This is consistent with previous studies

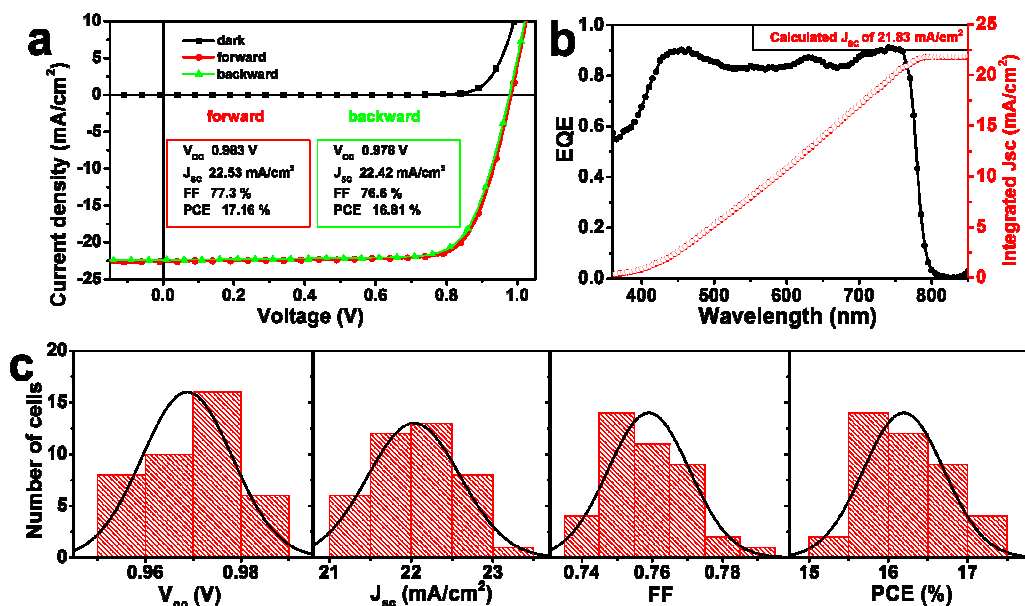

**Figure 7** (a) J-V curves and (b) external quantum efficiency (EQE) spectrum together with EQE data based integrated short-circuit current density ( $J_{sc}$ ) for the best performing perovskite solar cell. The J-V data were collected under AM 1.5G one sun illumination ( $100 \text{ mW/cm}^2$ ). (c) Histograms of  $J_{sc}$ , open-circuit voltage ( $V_{oc}$ ), fill factor (FF), and power conversion efficiency (PCE) of 40 cells, respectively.

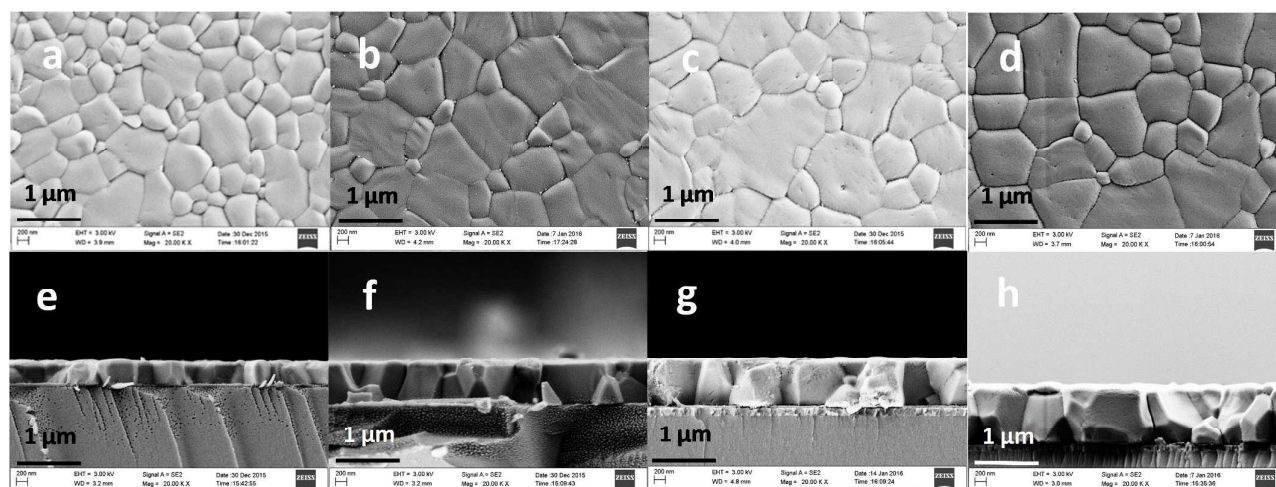

**Figure 8** Top-view (a-d) and cross-sectional (e-h) SEM image of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  perovskite films prepared with different thickness: (a, e)  $\sim 420$  nm, (b, f)  $\sim 650$  nm, (c, g)  $\sim 850$  nm, (d, h)  $\sim 1020$  nm.

reporting that charge traps are one of the origins of photocurrent hysteresis, and, consequently, the hysteresis can be reduced when the numerous voids and lots of crystal boundary due to small grains size that are the principle source for traps, are excluded.

In addition, aiming to clarify why the device showed a reduced photovoltaic performance, while their perovskite films exhibited the similar morphology (seen in Figure 2) and the same profile in PL spectra (seen in Figure 3a), we try to study the role of defects in the film. As we known, the temperature for perovskite nucleation and crystal growth are no more than  $100^\circ\text{C}$  that is the typical thermal annealing temperature as reported,<sup>25-26</sup> so a higher temperature thermal annealing may increase the formation possibility of crystal defects. Although similar profile were found in both PL spectra and morphology of perovskite films when the pre-annealing temperature was increased from  $100^\circ\text{C}$  to  $120^\circ\text{C}$ , a slight reduction of about 25% in PL intensity can be found (as shown in Figure S4), which can be indicated by the increased traps and defects.

Figure 7a shows the J-V curve of the best performing device obtained under  $100^\circ\text{C}$  pre-annealing conditions, which exhibited a  $J_{\text{SC}}$  of  $22.6\text{mA}/\text{cm}^2$ , a FF of 77.3%, a  $V_{\text{OC}}$  of 0.98 V, and a PCE of 17.2%. The external quantum efficiency (EQE) of the same device is shown in Figure 5b. The EQE value was higher than 80% over the whole visible region, reaching a maximum value of about 90%. The calculated  $J_{\text{SC}}$  from the EQE

**Table 1** Photovoltaic performance of perovskite solar cells with different thickness.

Thickness (nm)	$V_{\text{OC}}$ (V)	$J_{\text{SC}}$ ( $\text{mA}/\text{cm}^2$ )	FF	PCE (%)
$\sim 420$	0.969	-21.45	71.1	14.77
$\sim 650$	0.969	-21.97	76.2	16.23
$\sim 850$	0.983	-20.73	75.1	15.31
$\sim 1020$	0.983	-21.13	75.6	15.71

spectra is  $21.83\text{mA}/\text{cm}^2$ , which is comparable to our experimental value. To confirm the high reproducibility and slight efficiency deviation, the statistics of FF,  $J_{\text{SC}}$ ,  $V_{\text{OC}}$ , and PCE based on 40 devices are shown in Figure 7c. Here the photovoltaic performance deviation is  $22.03 \pm 0.57$   $\text{mA}/\text{cm}^2$  for  $J_{\text{SC}}$ , is  $0.759 \pm 0.011$  for FF, is  $0.969 \pm 0.009$  V for  $V_{\text{OC}}$ , and is  $16.19 \pm 0.51\%$  for PCE, respectively.

Notably, the grains of the perovskite films reached in-plane sizes up to  $1\text{--}2\ \mu\text{m}$ , which was between two and three times the grain size along the thickness direction of the film ( $\sim 650$  nm). Such a high aspect ratio growth of the perovskite grains and low trap density in these films indicated that the adopted fabrication process allow producing thicker perovskite films. We analyzed the performance of halide perovskite planar solar cells as a function of the perovskite film thickness variation. To control the thickness of the perovskite film, we adjusted the concentration of different solutions, obtaining thickness values from 420 to 1020 nm. The fabrication parameters for different thickness values are summarized in Table S1. Top-view and cross-sectional SEM images of perovskite films with different thickness are shown in Figure 8. All films with thickness from 420 nm to 1  $\mu\text{m}$  performed uniform and film-through grains. The photovoltaic parameters of the device with perovskite thickness from 420 nm to 1020 nm are listed in Table 1, as well as their photocurrent curves are shown in Figure S5a. The device did not exhibit a strong dependency of device performance on film thickness, of which even the thickest device (1  $\mu\text{m}$  film) still yields PCE approaching 15.7%. The EQE spectra of the devices is shown in Figure S5b, all the devices show the comparable EQE characteristics, and the calculated  $J_{\text{SC}}$  even for 1020-nm-thick device is  $21.14\text{mA}/\text{cm}^2$ , which suggests that negligible photogenerated charges loss happen in thick perovskite film because in that the charges could transport through a single grain without encountering grain boundaries and charge traps before being collected by the electrodes.

## Conclusion

In summary, we developed an effective procedure to produce  $\text{CH}_3\text{NH}_3\text{PbI}_3$  perovskite films with excellent crystallinity and large film-through grains. The pre-annealing step played an important role in promoting the growth of perovskite morphology and crystal behavior, resulting in a significant improvement of the material and electronic properties as well as a performance enhancement of the photovoltaic devices. The application of this procedure to solar cell fabrication yielded the highest PCE of 17.2% under AM 1.5 G, 100  $\text{mW}/\text{cm}^2$  test condition. The device did not exhibit a strong dependency of device performance on film thickness, even the thickest perovskite film prepared (1  $\mu\text{m}$  thick) was able to yield PCE approaching 15.7%. Based on our results, we believe that this sec-butyl alcohol based procedure may provide a cleaner and more effective strategy for the realization of high-performance perovskite solar cells.

## Acknowledgment

Parts of this work were supported by the National Basic Research Program of China (Grant No. 2015CB352005); the National Natural Science Foundation of China (No. 61525503/61378091/61405123/61505123); Guangdong Natural Science Foundation (No. S2012020011003 and 2014A030312008); Shenzhen Basic Research Project (JCYJ20130329115524512/ZDSYS20140430164957663/KQCX2 0140509172719305/ JCYJ20150525092940976); the Training Plan of Guangdong Province Outstanding Young Teachers in Higher Education Institutions (Yq2013142).

## Notes and references

- H. Zhou, Q. Chen, G. Li, S. Luo, T. B. Song, H. S. Duan, Z. Hong, J. You, Y. Liu and Y. Yang, *Science*, 2014, **345**, 542.
- J. Burschka, N. Pellet, S.-J. Moon, R. Humphry-Baker, P. Gao, M. K. Nazeeruddin and M. Grätzel, *Nature*, 2013, **499**, 316.
- W. A. Laban and L. Etgar, *Energy Environ. Sci.*, 2013, **6**, 3249–3253.
- H. Kim, K. G. Lim and T. W. Lee, *Energy Environ. Sci.*, 2016, **9**, 12–30.
- M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science*, 2012, **338**, 643.
- G. Xing, N. Mathews, S. Sun, S. S. Lim, Y. M. Lam, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Science*, 2013, **342**, 344.
- C. S. Ponce Jr., T. J. Savenije, M. Abdellah, K. Zheng, A. Yartsev, T. Pascher, T. Harlang, P. Chabera, T. Pullerits, A. Stepanov, J. P. Wolf and V. Sundström, *J. Am. Chem. Soc.*, 2014, **136**, 5189.
- F. Deschler, M. Price, S. Pathak, L. E. Klintberg, D. D. Jarausch, R. Higler, S. Hüttner, T. Leijtens, S. D. Stranks, H. J. Snaith, M. Atatüre, R. T. Phillips and R. H. Friend, *J. Phys. Chem. Lett.*, 2014, **5**, 1421.
- A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
- J. H. Im, C. R. Lee, J. W. Lee, S. W. Park and N. G. Park, *Nanoscale*, 2011, **3**, 4088–4093.
- I. Chung, B. Lee, J. He, R. P. H. Chang and M. G. Kanatzidis, *Nature*, 2012, **485**, 486–498.
- B. E. Hardin, H. J. Snaith and M. D. McGehee, *Nat. Photonics*, 2012, **6**, 162–169.
- W. S. Yang, J. H. Noh, N. J. Jeon, Y. C. Kim, S. Ryu, J. Seo and S. I. Seok, *Science*, 2015, **348**, 1234–1237.
- [http://www.nrel.gov/ncpv/images/efficiency\\_chart.jpg](http://www.nrel.gov/ncpv/images/efficiency_chart.jpg)
- M. A. Green, K. Emery, Y. Hishikawa, W. Warta and E. D. Dunlop, *Prog. Photovoltaics*, 2015, **23**, 1–9.
- S. Sigdel, A. Dubey, H. Elbohy, A. Aboagye, D. Galipeau, L. Zhang, H. Fong and Q. Qiao, *J. Mater. Chem. A*, 2014, **2**, 11448–11453.
- Y. Rong, Z. Tang, Y. Zhao, X. Zhong, S. Venkatesan, H. Graham, M. Patton, Y. Jing, A. M. Guloy and Y. Yao, *Nanoscale*, 2015, **7**, 10595–10599.
- J. A. Christians, P. A. Miranda Herrera and P. V. Kamat, *J. Am. Chem. Soc.*, 2015, **137**, 1530–1538.
- I. Chung, B. Lee, J. He, R. P. H. Chang and M. G. Kanatzidis, *Nature*, 2012, **485**, 486.
- Z. Xiao, C. Bi, Y. Shao, Q. Dong, Q. Wang, C. Wang, Y. Gao, J. Huang, *Energy Environ. Sci.*, 2014, **7**, 2619.
- A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050.
- J. M. Ball, M. M. Lee, A. Hey and H. J. Snaith, *Energy Environ. Sci.*, 2013, **6**, 1739.
- D. Liu and T. L. Kelly, *Nat. Photonics*, 2014, **8**, 133.
- Q. Wang, Q. Dong, Z. Xiao, Y. Yuan and J. Huang, *Energy Environ. Sci.*, 2014, **7**, 2359.
- N. J. Jeon, J. H. Noh, Y. C. Kim, W. S. Yang, S. Ryu and S. I. Seok, *Nat. Mater.*, 2014, **13**, 89.
- M. Xiao, F. Huang, W. Huang, Y. Dkhissi, Y. Zhu, J. Etheridge, A. Gray-Weale, U. Bach, Y. B. Cheng, L. Spiccia, *Angew. Chem.*, 2014, **126**, 10056.
- F. Zhang, J. Lian, J. Song, Y. Hao, P. Zeng and H. Niu, *J. Mater. Chem. A*, 2016, **4**, 3438–3445.
- Z. Xiao, Q. Dong, C. Bi, Y. Shao, Y. Yuan and J. Huang, *Adv. Mater.*, 2014, **26**, 6503–6509.
- J. Liu, C. Gao, X. He, Q. Ye, L. Ouyang, D. Zhuang, C. Liao, J. Mei and W. Lao, *Appl. Mater. Interfaces*, 2015, **7**, 24008–24015.
- K. Yan, M. Long, T. Zhang, Z. Wei, H. Chen, S. Yang and J. Xu, *J. Am. Chem. Soc.*, 2015, **137**, 4460.
- M. Qian, M. Li, X. B. Shi, H. Ma, Z. K. Wang and L. S. Liao, *J. Mater. Chem. A*, 2015, **3**, 13533–13539.
- J. You, Y. M. Yang, G. Li and Y. Yang, *Appl. Phys. Lett.*, 2014, **105**, 183902.
- H. Zhou, Q. Chen, Y. Liu and Y. Yang, *Science*, 2014, **345**, 542–546.