

Cite this: *Chem. Sci.*, 2020, 11, 6709

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Self-adjusting binding pockets enhance H<sub>2</sub> and CH<sub>4</sub> adsorption in a uranium-based metal–organic framework†

Dominik P. Halter,<sup>ab</sup> Ryan A. Klein,<sup>cd</sup> Michael A. Boreen,<sup>ae</sup> Benjamin A. Trump,<sup>d</sup> Craig M. Brown<sup>df</sup> and Jeffrey R. Long<sup>abg</sup>

A new, air-stable, permanently porous uranium(IV) metal–organic framework U(bdc)<sub>2</sub> (**1**, bdc<sup>2-</sup> = 1,4-benzenedicarboxylate) was synthesized and its H<sub>2</sub> and CH<sub>4</sub> adsorption properties were investigated. Low temperature adsorption isotherms confirm strong adsorption of both gases in the framework at low pressures. *In situ* gas-dosed neutron diffraction experiments with different D<sub>2</sub> loadings revealed a rare example of cooperative framework contraction ( $\Delta V = -7.8\%$ ), triggered by D<sub>2</sub> adsorption at low pressures. This deformation creates two optimized binding pockets for hydrogen ( $Q_{st} = -8.6$  kJ mol<sup>-1</sup>) per pore, in agreement with H<sub>2</sub> adsorption data. Analogous experiments with CD<sub>4</sub> ( $Q_{st} = -24.8$  kJ mol<sup>-1</sup>) and *N,N*-dimethylformamide as guests revealed that the binding pockets in **1** adjust by selective framework contractions that are unique for each adsorbent, augmenting individual host–guest interactions. Our results suggest that the strategic combination of binding pockets and structural flexibility in metal–organic frameworks holds great potential for the development of new adsorbents with an enhanced substrate affinity.

Received 27th April 2020  
Accepted 27th May 2020

DOI: 10.1039/d0sc02394a

rsc.li/chemical-science

## Introduction

Metal–organic frameworks are a class of chemically-robust, porous, and often rigid materials, composed of metal ions or clusters connected by bridging organic linkers.<sup>1–4</sup> The physical and chemical properties of these materials are highly tunable based on choice of metal and linker, and thus metal–organic frameworks have been proposed for a wealth of applications,<sup>5–9</sup> including catalysis,<sup>10–15</sup> sensing,<sup>16–18</sup> carbon capture,<sup>19–23</sup> gas separations,<sup>24–26</sup> and gas storage.<sup>27–31</sup> Metal–organic frameworks have attracted particular interest as candidate gas storage

materials for H<sub>2</sub> and CH<sub>4</sub> that could enable more efficient use of these energy carriers as cleaner fuel alternatives.<sup>32–38</sup> However, significant advances are still needed to develop frameworks capable of maintaining interactions with these guests at ambient temperatures.<sup>39–41</sup>

Two main strategies have been developed to achieve strong binding of H<sub>2</sub> and CH<sub>4</sub> in metal–organic frameworks. The first approach utilizes materials with coordinatively-unsaturated metal sites, which can polarize and strongly bind various guests.<sup>42,43</sup> Representative of this materials class is the framework Ni<sub>2</sub>(*m*-dobdc) (*m*-dobdc<sup>4-</sup> = 4,6-dioxido-1,3-benzenedicarboxylate), which is currently the top performing material for ambient temperature, physisorptive H<sub>2</sub> storage.<sup>33,34</sup> The other strategy exploits tight binding pockets in small-pore frameworks, which can engage in multiple, weak interactions with guest molecules to achieve strong overall guest binding, analogous to shape-selective molecular recognition in enzymes.<sup>44</sup> An example of how such cumulative dispersion forces can outperform strong interactions at open metal sites is the adsorption of CH<sub>4</sub> in Cu<sub>2</sub>(btc)<sub>3</sub> (HKUST-1, btc<sup>3-</sup> = 1,3,5-benzenetricarboxylate).<sup>45</sup> This material exhibits open metal sites and binding pockets in direct competition for CH<sub>4</sub> adsorption. Structural characterization of Cu<sub>2</sub>(btc)<sub>3</sub> dosed with low pressures of CD<sub>4</sub> confirmed that methane preferably adsorbs at the binding pockets inside small octahedral cages of the framework, rather than through direct interactions at the copper(II) open metal sites. The reason for this behavior is that the multiple interactions inside the pore give rise to a higher

<sup>a</sup>Department of Chemistry, University of California, Berkeley, CA 94720, USA. E-mail: jrlong@berkeley.edu

<sup>b</sup>Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA

<sup>c</sup>Chemistry and Nanoscience Department, National Renewable Energy Laboratory, Golden, CO 80401, USA

<sup>d</sup>Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, MD 20899, USA

<sup>e</sup>Chemical Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA

<sup>f</sup>Department of Chemical Engineering, University of Delaware, Newark, DE 19716, USA

<sup>g</sup>Department of Chemical and Biomolecular Engineering, University of California, Berkeley, CA 94720, USA

† Electronic supplementary information (ESI) available: Synthetic, analytical and crystallographic details. Single crystal X-ray crystallographic data was deposited in the Cambridge Crystallographic Data Centre database. CCDC 1996337. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0sc02394a



overall binding energy than that achieved with a CH<sub>4</sub> molecule adsorbed at a single copper(II) center ( $-21.8$  versus  $-9.4$  kJ mol<sup>-1</sup>, respectively).<sup>45</sup>

Cumulative dispersion interactions between guest molecules and framework pockets decrease exponentially with the adsorbate–framework distances ( $F \propto 1/r^6$ ), and therefore require a precise geometric fit between guest and binding pocket.<sup>46</sup> For example, as a result of its smaller kinetic diameter relative to CH<sub>4</sub>,<sup>47</sup> H<sub>2</sub> preferentially binds at the open metal sites of Cu<sub>2</sub>(btc)<sub>3</sub>, rather than in the hexagonal pockets.<sup>48</sup> The development of new frameworks with efficient binding pockets therefore requires precise optimization for each adsorbate of interest, although achieving this goal by structural design remains a significant challenge.

An alternative approach to circumvent the synthetic intricacy of developing materials with optimized guest-specific binding pockets, are materials that combine small binding pockets with moderate framework flexibility.<sup>49</sup> Synthetic tuning can thus be used to design crude binding pockets, which are capable of self-adjusting in response to guest adsorption. Together, these design features could enable access to optimal binding pocket geometries for a variety of guests within the same material. Such molecular recognition often relies on initially weak host-guest interactions, highlighting the importance to precisely adjust the energy required for the deformation of a flexible framework and the energy released by guest adsorption.<sup>50–52</sup>

Flexibility is typically introduced into metal–organic frameworks by utilizing organic linkers with non-rigid stems, by interconnecting metals with non-chelating linkers, or by cross-linking two-dimensional frameworks with additional ditopic but weakly binding linkers.<sup>53–55</sup> Prominent examples are M(OH)(bdc) (MIL-53; bdc<sup>2-</sup> = 1,4-benzenedicarboxylate; M = Fe, Cr, Sc, Al, or Ga)<sup>56–60</sup> and M<sub>3</sub>(O)(OH)(H<sub>2</sub>O)<sub>2</sub>(bdc)<sub>3</sub> (MIL-88; M = Fe, Cr).<sup>61</sup> These frameworks undergo drastic geometric distortions upon guest adsorption, often referred to as framework swelling, which can induce a substantial unit cell volume increase of up to 74%, as shown for example by CO<sub>2</sub> adsorption in Fe(OH)(bdc).<sup>62</sup> Such large structural changes are too extreme to drive the subtle binding pocket adjustments sought here. One could instead envision limiting the flexibility of non-chelating bdc<sup>2-</sup> linkers by substantially increasing the number of metal–ligand bonds per metal node. A higher coordination number should limit structural rearrangements by causing steric encumbrance around the metal nodes and increase rigidity by further crosslinking the resulting material. Additionally, a higher ligand-to-metal ratio could result in smaller pore sizes and better binding pockets.

With their tendency to adopt high coordination numbers, actinides are well suited as metal nodes for the development of such materials.<sup>63</sup> We chose depleted uranium to test our hypothesis, as it is only mildly radioactive and because a limited but growing number of uranium-based frameworks have already been reported and could guide the synthesis.<sup>64</sup> Inspired by previous work on the synthesis of porous metal–organic frameworks from uranium(IV) and bdc<sup>2-</sup> linkers,<sup>65</sup> we synthesized a new, three-dimensional U(bdc)<sub>2</sub> phase (**1**) with permanent porosity and a moderate level of structural flexibility. Using

a combination of gas adsorption studies and *in situ* powder neutron diffraction experiments, we demonstrate that this framework undergoes an adjustable contraction of its pores to accommodate and strongly bind H<sub>2</sub> and CH<sub>4</sub>, with different levels of contraction and host-guest interactions for each molecule.

## Results and discussion

The compound U(bdc)<sub>2</sub>·4H<sub>2</sub>O (**1**-H<sub>2</sub>O) was synthesized through the reaction of U<sub>4</sub>(1,4-dioxane)<sub>2</sub> with H<sub>2</sub>bdc in *N,N*-dimethylformamide (DMF, <0.15% water content as received) at 140 °C under argon inside a Parr autoclave. After three days, the material was isolated in 79% yield as air-stable, thin emerald green needle-shaped crystals. Single crystal X-ray diffraction analysis was used to determine the structure of **1**-H<sub>2</sub>O (Fig. 1), and selected bond distances and angles are given in Table S5 of the ESI.† We note that powder X-ray diffraction patterns collected for bulk samples of **1**-H<sub>2</sub>O match the simulated pattern determined from single-crystal data, confirming the bulk purity of the crystalline material (see ESI, Fig. S7†).

Compound **1**-H<sub>2</sub>O crystallizes in the space group *C2/c* and features eight-coordinate uranium centers in a distorted square-antiprismatic environment. Each uranium(IV) is



Fig. 1 (a) Single crystal X-ray diffraction structure of **1**-H<sub>2</sub>O viewed along the *c*-axis, showing the parallelepipedal pores. (b) Truncated structure showing one of the pores of **1**-H<sub>2</sub>O along the crystallographic *c*-axis, with the two identical binding pockets of the pore depicted as blue spheres. (c) The same view as in (b), rotated by 90° to visualize the bowl-shaped arrangement of three bdc<sup>2-</sup> linkers that form the cap of each binding pocket. Orange, red, and grey spheres represent U, O, and C atoms, respectively; solvent and H atoms are omitted for clarity.



coordinated to one oxygen atom of eight different  $\text{bdc}^{2-}$  linkers, and all linkers are coordinated to four different uranium ions in a bridging fashion. This motif results in an overall framework structure consisting of distorted parallelepipedal pores (Fig. 1a) formed by chains of uranium(IV) centers that propagate along the crystallographic  $c$ -axis (see ESI, Fig. S17†) and are bridged by  $\text{bdc}^{2-}$  linkers bent in a concave and convex fashion.

Each pore is formed by two opposing, inwardly bent  $\text{bdc}^{2-}$  linkers at the sides and is capped at the top and bottom by a bowl-shaped arrangement of three additional  $\text{bdc}^{2-}$  linkers (Fig. 1b and c). The resulting geometry yields two identical binding pockets per pore that are  $\sim 5$  Å in diameter and related by an inversion center.

In the as-synthesized framework, each binding pocket is occupied by two disordered water molecules, yielding the composition  $\text{U}(\text{bdc})_2 \cdot 4\text{H}_2\text{O}$ , which was also confirmed by thermogravimetric analysis (see ESI, Fig. S6†). While disorder precluded modeling of any specific interactions, the guest water molecules are likely to engage in hydrogen bonding with each other and with the highly polarized U–O bonds. We note that the structure of the pores is such that guests could engage in a variety of additional interactions, including with the linker  $\pi$ -systems and arene C–H bonds.

Activated  $\text{U}(\text{bdc})_2$  (**1**) was obtained by heating **1**– $\text{H}_2\text{O}$  at 260 °C for 10 h under dynamic vacuum. Combustion analysis confirmed the empirical formula for **1** and the removal of guest water molecules. Nitrogen adsorption isotherms obtained at 77 K for four different samples revealed the activated material is permanently porous, with an average Langmuir surface area of  $497 \pm 6 \text{ m}^2 \text{ g}^{-1}$  (see ESI, Fig. S1†). Powder X-ray diffraction analysis confirmed that **1** remains crystalline with a slightly different structure from that of its solvated analogue (see ESI, Fig. S7†). Interestingly, while many flexible frameworks contract or even fully collapse to a nonporous structure upon solvent removal,<sup>37,66–68</sup> activation of **1**– $\text{H}_2\text{O}$  to give **1** results in an expansion of the framework along the crystallographic  $b$ -axis, from 12.598(1) to 12.812(1) Å. This change results in an increase in the unit cell volume from 1887.4(3) to 1902.1(2) Å<sup>3</sup>, while retaining the  $C2/c$  space group. This behavior upon guest removal indicates that the framework binding pockets are indeed able to contract to improve interactions with adsorbates.

We sought to study the flexibility of **1** in more detail using  $\text{H}_2$  and  $\text{CH}_4$  (with kinetic diameters of 2.9 and 3.8 Å, respectively)<sup>18</sup> as probe molecules of interest for potential gas storage applications. The low-pressure  $\text{H}_2$  adsorption isotherm for  $\text{U}(\text{bdc})_2$  at 77 K exhibits an initial steep rise to  $\sim 3.5 \text{ mmol g}^{-1}$  at 115 mbar, which is indicative of the presence of strong adsorption sites (Fig. 2). We note that this loading corresponds to the theoretical capacity expected for adsorption of one  $\text{H}_2$  molecule per adsorption pocket (two per pore). With further increasing pressure, the quantity of adsorbed  $\text{H}_2$  increases very gradually to an apparent saturation value of  $\sim 4.9 \text{ mmol g}^{-1}$  at 1.2 bar. A dual site Langmuir model was used to fit independently  $\text{H}_2$  adsorption data collected at 77 and 87 K (see Section 3 of the ESI, Fig. S2 and Table S1†), and the Clausius–Clapeyron equation was then employed to calculate the isosteric heat ( $Q_{\text{st}}$ ) of  $\text{H}_2$  adsorption as a function of loading (Fig. 2, inset). For loadings

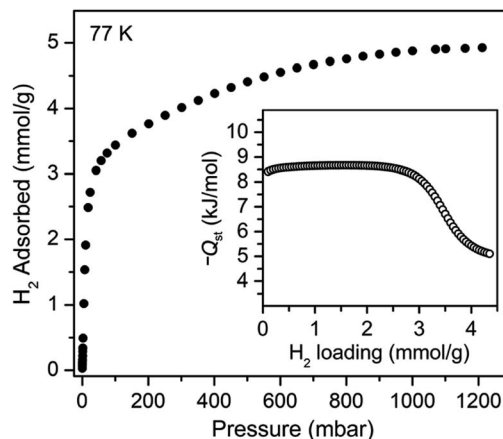


Fig. 2 Hydrogen adsorption isotherm for **1**, measured at 77 K. Inset: loading-dependent isosteric heat of adsorption ( $Q_{\text{st}}$ ) for  $\text{H}_2$  in **1**.

up to 2.5  $\text{mmol g}^{-1}$ ,  $\text{H}_2$  adsorbs exclusively at primary binding sites in the framework pockets (see below) to give a  $Q_{\text{st}}$  of  $-8.6 \text{ kJ mol}^{-1}$ . Notably, this value is larger in magnitude than the  $\text{H}_2$  isosteric heat of adsorption in activated carbon materials ( $-5.0$  to  $-6.4 \text{ kJ mol}^{-1}$ )<sup>69</sup> and the majority of frameworks with coordinatively-saturated metal sites ( $-4.1$  to  $-8.8 \text{ kJ mol}^{-1}$ ).<sup>70</sup>

The  $\text{CH}_4$  adsorption isotherm for **1** obtained at 195 K exhibits a steep uptake similar to that characterized for  $\text{H}_2$  at low pressures, again indicative of strong interactions between  $\text{CH}_4$  and the binding pockets of the framework (Fig. 3). A dual site Langmuir model was used to simultaneously fit isotherm data collected at 195, 273, 298, and 308 K, and the Clausius–Clapeyron equation was then employed to calculate a value of  $Q_{\text{st}} = -24.8 \text{ kJ mol}^{-1}$  at low loadings (see ESI, Fig. S5†). Notably, this value surpasses that determined for  $\text{Zn}_4\text{O}(\text{bdc})_3$  (MOF-5;  $Q_{\text{st}} = -12.3 \text{ kJ mol}^{-1}$ ) and even values for frameworks with snugly fitting pore window, such as  $\text{Cu}_2(\text{btc})_3$  ( $Q_{\text{st}} = -17.1 \text{ kJ mol}^{-1}$ ), or strongly polarizing open metal cation sites, as in  $\text{Ni}_2(\text{dobdc})$  ( $\text{dobdc}^{4-} = 2,5\text{-dioxido-1,4-benzenedicarboxylate}$ ;  $Q_{\text{st}} = -20.6 \text{ kJ mol}^{-1}$ ).<sup>41,45</sup> It is clear that the binding pockets in

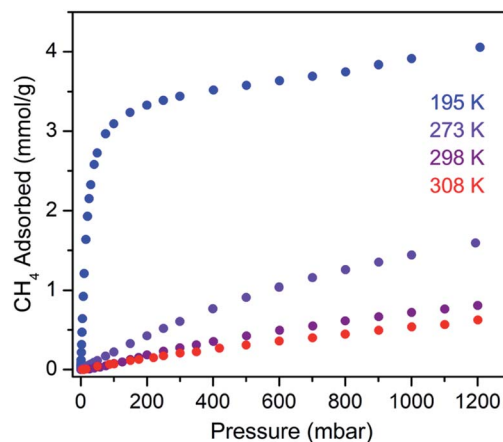


Fig. 3 Methane adsorption isotherms for **1**, measured at the indicated temperatures.



U(bdc)<sub>2</sub> can strongly interact with both H<sub>2</sub> and CH<sub>4</sub>, despite their different sizes, which suggests that the framework may distort or flex to optimize interactions with different guest molecules. In order to study the framework-guest interactions in more detail, we turned to *in situ* gas-dosing powder neutron diffraction. The powder neutron diffraction pattern of activated **1** at 9 K was first collected as a reference for gas dosing experiments (see ESI, Fig. S9†). Dosing with 0.3 equiv. of D<sub>2</sub> per pore results in clear changes in the powder pattern, particularly visible at low values of scattering angle  $2\theta$  (Fig. 4 and S10†). Specifically, the reflections of **1** decrease in intensity while a second set of peaks arises, ascribed to a new crystalline phase **1-D**<sub>2</sub>. Upon increasing the loading to 0.7 equiv. of D<sub>2</sub>, both phases are still present, although the peaks of **1** diminish further and the peaks of newly formed **1-D**<sub>2</sub> gain in intensity (Fig. 4 and S11†). The two phases coexist up to a loading of at least 1.5 equiv. D<sub>2</sub> per pore (see ESI, Fig. S12†), and their interconversion is best followed by evaluating the high intensity, low angle peaks at  $2\theta \approx 11.85^\circ$  for **1** and at  $2\theta \approx 12.63^\circ$  for **1-D**<sub>2</sub> in Fig. 4. These data strongly suggest that cooperative effects drive an adsorbate-induced framework distortion from **1** to **1-D**<sub>2</sub>. Such a mechanism is in contrast to a gradual and homogeneous uptake of D<sub>2</sub>, or a gradually changing degree of distortion depending on the D<sub>2</sub>-loading. As a result, before achieving saturation loading, some individual crystallites of the sample will be distorted, such that both binding pockets per pore are occupied with a D<sub>2</sub> molecule, while others will remain in the activated structure of **1**. At the highest D<sub>2</sub> dosing level of 2.5 equiv. per pore, the diffraction pattern of the sample contains only reflections associated with **1-D**<sub>2</sub> (see ESI, Fig. S13†).

*In situ* powder neutron diffraction experiments were also carried out by dosing **1** with 0.7 and 1.5 equiv. of CD<sub>4</sub> (Fig. S14 and S15†). The data from these experiments suggest a similar cooperative transformation from **1** to an adsorbed phase **1-CD**<sub>4</sub>.



Fig. 4 Rietveld refinement fits of powder neutron diffraction patterns ( $\lambda = 2.0772 \text{ \AA}$ ,  $T = 9 \text{ K}$ ) collected for activated **1** and activated **1** dosed with 0.3, 0.7, and 1.5 equiv. of D<sub>2</sub> per pore. Black (lower) and blue (upper) tick marks indicate calculated Bragg peak positions for **1** and the D<sub>2</sub> adsorbed phase, **1-D**<sub>2</sub>, respectively. Arrows indicate peaks that best illustrate the conversion of **1** to **1-D**<sub>2</sub> with increasing D<sub>2</sub> loading.

Rietveld refinements were applied to all powder neutron diffraction data (see Section 6 in the ESI†) in order to elucidate adsorbate-induced structural deformations and characterize specific adsorption sites for D<sub>2</sub> and CD<sub>4</sub>. Selected unit cell parameters determined for the different structures are summarized in Table 1. Based on unit cell volume, **1** contracts to a greater extent to accommodate D<sub>2</sub> than it does in the presence of CH<sub>4</sub>.

Surprisingly, a structural comparison of **1** with **1-D**<sub>2</sub> and **1-CD**<sub>4</sub> reveals an almost constant coordination environment around the uranium nodes in each phase. The framework flexibility instead relies on a tilting of the parallelepipedal pores, which is clearly seen by comparing the pore geometries of **1** and **1-D**<sub>2</sub> dosed with 2.5 equiv. D<sub>2</sub>, as shown in Fig. 5a. Here, each structure is overlaid with an idealized parallelogram with corners defined by the uranium ions. Dosing with 2.5 equiv. of D<sub>2</sub> results in a change of the idealized parallelogram angles,  $\varphi_1$  and  $\varphi_2$ , from  $77.1(1)^\circ$  and  $102.902(3)^\circ$  in **1** to  $65.03(6)^\circ$  and  $114.973(1)^\circ$  in **1-D**<sub>2</sub>. In order to accommodate this rearrangement, the two unique dihedral angles,  $\omega_1$  and  $\omega_2$ , between the bdc<sup>2-</sup> O-C-O planes and the neighboring O-U...U-O planes adjust from  $151(1)^\circ$  and  $168.4(9)^\circ$  in **1** to  $138.5(4)^\circ$  and  $174.9(5)^\circ$  in **1-D**<sub>2</sub> (Fig. 5b).

The resulting hinge-type bending between the UO<sub>8</sub> nodes and linkers is analogous to the change that occurs in the structure of the flexible framework Cr(OH)(bdc) upon water adsorption.<sup>53</sup> In particular, water adsorption is accompanied by a unit cell volume decrease from 1486.1 to 1012.6 Å<sup>3</sup>, as well as a decrease of the symmetrical dihedral angles,  $\omega$ , from  $179.8^\circ$  to  $162.3^\circ$ . The analogous idealized Cr...Cr...Cr angles  $\varphi_1$  and  $\varphi_2$  in



Fig. 5 (a) Illustration of pores in **1** and **1-D**<sub>2</sub> (dosed with 2.5 equiv. D<sub>2</sub> per pore). The pore contraction upon D<sub>2</sub> dosing is highlighted by the colored blue and purple areas within the crystallographic *ab*-plane. Tilting of the pores to facilitate contraction is illustrated by idealized parallelograms (dashed lines) with corners defined by uranium atoms. Adsorbed D<sub>2</sub> molecules inside the pores of **1-D**<sub>2</sub> are represented as aquamarine spheres for adsorption site I and as brown spheres for adsorption site II. Each D<sub>2</sub> super atom at site II is shared between two neighboring pores, accordingly the two depicted site II super atoms together account for an occupancy of one D<sub>2</sub> molecule per pore. (b) Comparison of the dihedral angles  $\omega_1$  as described in the text ( $\omega_2$  is not shown, but is the corresponding angle at the other end of the linker), representing the main structural distortion undergone by **1** upon adsorption of D<sub>2</sub>. Orange, red, and grey spheres represent U, O, and C atoms, respectively.







Fig. 6 (a) Neutron powder diffraction structure of  $D_2$  adsorbed at site I in  $1-D_2$  after dosing **1** with 2.5 equiv.  $D_2$  per pore. (b) Neutron powder diffraction structure of  $CD_4$  adsorbed at site I in  $1-CD_4$  after dosing **1** with 1.5 equiv.  $CD_4$  per pore. (c) Powder X-ray diffraction structure of DMF adsorbed inside the pore of  $U(bdc)_2$ . For clarity, only selected interactions of DMF with the framework are depicted. All framework–guest interactions are depicted as aquamarine colored dashed lines. For clarity in (a) and (b), the pore is truncated and cut in half diagonally, showing only one of the two adsorption pockets of the pore. Orange, red, grey, blue, aquamarine, and white spheres represent U, O, C, N, D, and H atoms, respectively.

refinement of powder X-ray diffraction data obtained at 298 K (see ESI, Fig. S8†). The framework indeed contracts to optimize interactions with DMF, but the unit cell volume decreases by only 1.9% (compared to 7.8% and 3.4% in the cases of 2.5 equiv.  $D_2$  and 1.5 equiv.  $CD_4$ , respectively) and the pocket diameter only decreases to 4.2 Å. While two molecules of the smaller guests  $D_2$  and  $CD_4$  can simultaneously occupy the two binding pockets in each pore, the larger DMF molecule occupies the whole pore space, bridging both pockets (Fig. 6c). As a result, DMF is stabilized by seven of the eight  $bdc^{2-}$  linkers that form the surrounding pore. While precise contact distances are obscured by disorder of DMF over two positions in the structure, the general identity of host–guest interactions in  $1-DMF$  is clear. In particular, DMF binds through eight  $H\cdots H$  contacts, three  $C-H\cdots\pi$ -interactions, three  $O\cdots H$  contacts involving the carbonyl and arene  $C-H$  moieties, and interactions of two DMF  $C-H$  groups with O atoms of two  $UO_8$  nodes (all distances between 2 and 4 Å).

## Conclusions

Porous adsorbents with small binding pockets can engage in strong, selective host–guest interactions, and are therefore of interest for applications including gas capture and storage. However, it remains a significant challenge to tune a binding pocket structure to optimize interactions with a specific target molecule. In this work, we show that combining moderate flexibility with small pores in the new flexible metal–organic framework  $U(bdc)_2$  (**1**) eliminates the need for precise tuning of pore geometry. Indeed, this material is capable of uniquely adjusting its pore and binding pocket geometry to optimize host–guest interactions in the presence of even very weakly adsorbing molecules, such as  $H_2$  and  $CH_4$ . Temperature-dependent  $H_2$  and  $CH_4$  adsorption isotherms yielded isosteric heats of adsorption of  $-8.6$  and  $-24.8$   $\text{kJ mol}^{-1}$  for  $H_2$  and  $CH_4$ , respectively, confirming comparatively strong interactions of **1** with both gases, despite their different sizes. *In situ* powder neutron diffraction experiments with  $D_2$  and  $CD_4$  revealed that

cooperative effects drive a spontaneous adjustment of the binding pockets in **1** to generate multiple stabilizing interactions between each adsorbate and the framework, which are not achieved without pore contraction. Altogether, our results demonstrate the utility of frameworks featuring self-adjusting binding pockets that can flex in response to different guest molecules. The design principles applied for our model material **1** are transferable to non-radioactive frameworks and suggest further exploration of such materials will be advantageous in the search for adsorbents with improved gas storage properties.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the Hydrogen Materials – Advanced Research Consortium (HyMARC), established as part of the Energy Materials Network under the U. S. Department of Energy, Office of Energy Efficiency and Renewable Energy, Fuel Cell Technologies Office, under Contract DE-AC02-05CH11231. Powder X-ray diffraction data were collected on beamline 17-BM at the Advanced Photon Source at Argonne National Laboratory, which is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-06CH11357. Single-crystal X-ray diffraction data were collected at the Advanced Light Source beamline 12.2.1 at Lawrence Berkeley National Laboratory. The Advanced Light Source (ALS) is supported by the Director, Office of Science, Office of Basic Energy Sciences, of the U.S. DOE under Contract No. DE-AC02-05CH11231. D. P. H. thanks the Alexander von Humboldt Foundation for a Feodor Lynen Postdoctoral Research Fellowship. R. A. K. acknowledges research support from the U.S. Department of Energy, Office of Energy Efficiency and Renewable Energy, Fuel Cell Technologies Office, under Contract DE-AC36-08GO28308. We further thank Colin A. Gould



for helpful discussions, Ari Turkiewicz for assistance with single-crystal X-ray diffraction, Henry Z. H. Jiang and Maria V. Paley for help with acquiring high resolution powder X-ray diffraction data, and Dr Katie R. Meihaus for editorial assistance.

## References

- H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444.
- N. Stock and S. Biswas, *Chem. Rev.*, 2012, **112**, 933.
- M. Eddaoudi, J. Kim, N. Rosi, D. Vodak, J. Wachter, M. O'Keeffe and O. M. Yaghi, *Science*, 2002, **295**, 469.
- S. Yuan, L. Feng, K. Wang, J. Pang, M. Bosch, C. Lollar, Y. Sun, J. Qin, X. Yang, P. Zhang, Q. Wang, L. Zou, Y. Zhang, L. Zhang, Y. Fang, J. Li and H.-C. Zhou, *Adv. Mater.*, 2018, **30**, 1704303.
- T. Islamoglu, S. Goswami, Z. Li, A. J. Howarth, O. K. Farha and J. T. Hupp, *Acc. Chem. Res.*, 2017, **50**, 805.
- W. Lu, Z. Wei, Z.-Y. Gu, T.-F. Liu, J. Park, J. Park, J. Tian, M. Zhang, Q. Zhang, T. Gentle, M. Bosch and H.-C. Zhou, *Chem. Soc. Rev.*, 2014, **43**, 5561.
- A. U. Czaja, N. Trukhan and U. Müller, *Chem. Soc. Rev.*, 2009, **38**, 1284.
- C. H. Hendon, A. J. Rieth, M. D. Korzyński and M. Dincă, *ACS Cent. Sci.*, 2017, **3**, 554.
- A. Bétard and R. A. Fischer, *Chem. Rev.*, 2012, **112**, 1055.
- Q. Wang and D. Astruc, *Chem. Rev.*, 2020, **120**, 1438.
- D. J. Xiao, E. D. Bloch, J. A. Mason, W. L. Queen, M. R. Hudson, N. Planas, J. Borycz, A. L. Dzubak, P. Verma, K. Lee, F. Bonino, V. Crocell, J. Yano, S. Bordiga, D. G. Truhlar, L. Gagliardi, C. M. Brown and J. R. Long, *Nat. Chem.*, 2014, **6**, 590.
- S. A. Burgess, A. Kassie, S. A. Baranowski, K. J. Fritzsche, K. Schmidt-Rohr, C. M. Brown and C. R. Wade, *J. Am. Chem. Soc.*, 2016, **138**, 1780.
- S. M. Cohen, Z. Zhang and J. A. Boissonnault, *Inorg. Chem.*, 2016, **55**, 7281.
- Y.-B. Huang, J. Liang, X.-S. Wang and R. Cao, *Chem. Soc. Rev.*, 2017, **46**, 126.
- J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450.
- L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. van Duyne and J. T. Hupp, *Chem. Rev.*, 2012, **112**, 1105.
- M. G. Campbell, D. Sheberla, S. F. Liu, T. M. Swager and M. Dincă, *Angew. Chem., Int. Ed.*, 2015, **54**, 4349.
- I. Stassen, N. Burch, A. Talin, P. Falcaro, M. Allendorf and R. Ameloot, *Chem. Soc. Rev.*, 2017, **46**, 3185.
- K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T.-H. Bae and J. R. Long, *Chem. Rev.*, 2012, **112**, 724.
- T. M. McDonald, J. A. Mason, X. Kong, E. D. Bloch, D. Gygi, A. Dani, V. Crocellà, F. Giordanino, S. O. Odoh, W. S. Drisdell, B. Vlasisavljevich, A. L. Dzubak, R. Poloni, S. K. Schnell, N. Planas, K. Lee, T. Pascal, L. F. Wan, D. Prendergast, J. B. Neaton, B. Smit, J. B. Kortright, L. Gagliardi, S. Bordiga, J. A. Reimer and J. R. Long, *Nature*, 2015, **519**, 303.
- R. L. Siegelman, P. J. Milner, A. C. Forse, J.-H. Lee, K. A. Colwell, J. B. Neaton, J. A. Reimer, S. C. Weston and J. R. Long, *J. Am. Chem. Soc.*, 2019, **141**, 13171.
- M. Ding, R. W. Flaig, H.-L. Jiang and O. M. Yaghi, *Chem. Soc. Rev.*, 2019, **48**, 2783.
- D. J. Babu, G. He, J. Hao, M. T. Vahdat, P. A. Schouwink, M. Mensi and K. V. Agrawal, *Adv. Mater.*, 2019, **31**, 1900855.
- B. R. Barnett, M. I. Gonzalez and J. R. Long, *Trends Chem.*, 2019, **1**, 159.
- H. Li, K. Wang, Y. Sun, C. T. Lollar, J. Li and H.-C. Zhou, *Mater. Today*, 2018, **21**, 108.
- D. E. Jaramillo, D. A. Reed, H. Z. H. Jiang, J. Oktawiec, M. W. Mara, A. C. Forse, D. J. Lussier, R. A. Murphy, M. Cunningham, V. Colombo, D. K. Shuh, J. A. Reimer and J. R. Long, *Nat. Mater.*, 2020, **19**, 517.
- B. Li, H.-M. Wen, W. Zhou and B. Chen, *J. Phys. Chem. Lett.*, 2014, **5**, 3468.
- R. E. Morris and P. S. Wheatley, *Angew. Chem., Int. Ed.*, 2008, **47**, 4966.
- D. A. Reed, D. J. Xiao, H. Z. H. Jiang, K. Chakarawet, J. Oktawiec and J. R. Long, *Chem. Sci.*, 2020, **11**, 1698.
- S. Ma and H.-C. Zhou, *Chem. Commun.*, 2010, **46**, 44.
- I. Senkowska, E. Barea, J. A. R. Navarro and S. Kaskel, *Microporous Mesoporous Mater.*, 2012, **156**, 115.
- P. Garcia-Holley, B. Schweitzer, T. Islamoglu, Y. Liu, L. Lin, S. Rodriguez, M. H. Weston, J. T. Hupp, D. A. Gómez-Gualdrón, T. Yildirim and O. K. Farha, *ACS Energy Lett.*, 2018, **3**, 748.
- M. T. Kapelewski, S. J. Geier, M. R. Hudson, D. Stück, J. A. Mason, J. N. Nelson, D. J. Xiao, Z. Hulvey, E. Gilmour, S. A. FitzGerald, M. Head-Gordon, C. M. Brown and J. R. Long, *J. Am. Chem. Soc.*, 2014, **136**, 12119.
- M. T. Kapelewski, T. Runčevski, J. D. Tarver, H. Z. H. Jiang, K. E. Hurst, P. A. Parilla, A. Ayala, T. Gennett, S. A. FitzGerald, C. M. Brown and J. R. Long, *Chem. Mater.*, 2018, **30**, 8179.
- A. Ahmed, S. Seth, J. Purewal, A. G. Wong-Foy, M. Veenstra, A. J. Matzger and D. J. Siegel, *Nat. Commun.*, 2019, **10**, 1568.
- Y. He, W. Zhou, G. Qian and B. Chen, *Chem. Soc. Rev.*, 2014, **43**, 5657.
- J. A. Mason, J. Oktawiec, M. K. Taylor, M. R. Hudson, J. Rodriguez, J. E. Bachman, M. I. Gonzalez, A. Cervellino, A. Guagliardi, C. M. Brown, P. L. Llewellyn, N. Masciocchi and J. R. Long, *Nature*, 2015, **527**, 357.
- K. V. Kumar, K. Preuss, M.-M. Titirici and F. Rodríguez-Reinoso, *Chem. Rev.*, 2017, **117**, 1796.
- M. D. Allendorf, Z. Hulvey, T. Gennett, A. Ahmed, T. Autrey, J. Camp, E. Seon Cho, H. Furukawa, M. Haranczyk, M. Head-Gordon, S. Jeong, A. Karkamkar, D.-J. Liu, J. R. Long, K. R. Meihaus, I. H. Nayyar, R. Nazarov, D. J. Siegel, V. Stavila, J. J. Urban, S. P. Veccham and B. C. Wood, *Energy Environ. Sci.*, 2018, **11**, 2784.
- M. P. Suh, H. J. Park, T. K. Prasad and D.-W. Lim, *Chem. Rev.*, 2012, **112**, 782.



- 41 J. A. Mason, M. Veenstra and J. R. Long, *Chem. Sci.*, 2014, **5**, 32.
- 42 M. I. Gonzalez, J. A. Mason, E. D. Bloch, S. J. Teat, K. J. Gagnon, G. Y. Morrison, W. L. Queen and J. R. Long, *Chem. Sci.*, 2017, **8**, 4387.
- 43 D. Denysenko, M. Grzywa, J. Jelic, K. Reuter and D. Volkmer, *Angew. Chem., Int. Ed.*, 2014, **53**, 5832.
- 44 P. G. Boyd, A. Chidambaram, E. García-Díez, C. P. Ireland, T. D. Daff, R. Bounds, A. Gładysiak, P. Schouwink, S. M. Moosavi, M. M. Maroto-Valer, J. A. Reimer, J. A. R. Navarro, T. K. Woo, S. Garcia, K. C. Stylianou and B. Smit, *Nature*, 2019, **576**, 253.
- 45 Z. Hulvey, B. Vlasisavljevich, J. A. Mason, E. Tsivion, T. P. Dougherty, E. D. Bloch, M. Head-Gordon, B. Smit, J. R. Long and C. M. Brown, *J. Am. Chem. Soc.*, 2015, **137**, 10816.
- 46 D. G. Truhlar, *J. Chem. Educ.*, 2019, **96**, 1671.
- 47 N. Mehio, S. Dai and D.-e. Jiang, *J. Phys. Chem. A*, 2014, **118**, 1150.
- 48 Y. Liu, C. M. Brown, D. A. Neumann, V. K. Peterson and C. J. Kepert, *J. Alloys Compd.*, 2007, **446–447**, 385.
- 49 A. P. Katsoulidis, D. Antypov, G. F. S. Whitehead, E. J. Carrington, D. J. Adams, N. G. Berry, G. R. Darling, M. S. Dyer and M. J. Rosseinsky, *Nature*, 2019, **565**, 213.
- 50 Y. Gu, J.-J. Zheng, K.-I. Otake, K. Sugimoto, N. Hosono, S. Sakaki, F. Li and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2020, DOI: 10.1002/anie.202003186.
- 51 F.-X. Coudert, M. Jeffroy, A. H. Fuchs, A. Boutin and C. Mellot-Draznieks, *J. Am. Chem. Soc.*, 2008, **130**, 14294.
- 52 B. Chen, S. Xiang and G. Qian, *Acc. Chem. Res.*, 2010, **43**, 1115.
- 53 A. Schneemann, V. Bon, I. Schwedler, I. Senkovska, S. Kaskel and R. A. Fischer, *Chem. Soc. Rev.*, 2014, **43**, 6062.
- 54 L. Sarkisov, R. L. Martin, M. Haranczyk and B. Smit, *J. Am. Chem. Soc.*, 2014, **136**, 2228.
- 55 J.-P. Zhang, H.-L. Zhou, D.-D. Zhou, P.-Q. Liao and X.-M. Chen, *Natl. Sci. Rev.*, 2018, **5**, 907.
- 56 C. Serre, F. Millange, C. Thouvenot, M. Noguès, G. Marsolier, D. Louër and G. Férey, *J. Am. Chem. Soc.*, 2002, **124**, 13519.
- 57 M. Vougo-Zanda, J. Huang, E. Anokhina, X. Wang and A. J. Jacobson, *Inorg. Chem.*, 2008, **47**, 11535.
- 58 G. Férey, M. Latroche, C. Serre, F. Millange, T. Loiseau and A. Percheron-Guégan, *Chem. Commun.*, 2003, 2976.
- 59 F. Millange, N. Guillou, M. E. Medina, G. Férey, A. Carlin-Sinclair, K. M. Golden and R. I. Walton, *Chem. Mater.*, 2010, **22**, 4237.
- 60 J. P. S. Mowat, S. R. Miller, A. M. Z. Slawin, V. R. Seymour, S. E. Ashbrook and P. A. Wright, *Microporous Mesoporous Mater.*, 2011, **142**, 322.
- 61 S. Surblé, C. Serre, C. Mellot-Draznieks, F. Millange and G. Férey, *Chem. Commun.*, 2006, 284.
- 62 N. Guillou, S. Bourrelly, P. L. Llewellyn, R. I. Walton and F. Millange, *CrystEngComm*, 2015, **17**, 422.
- 63 S. R. Daly, P. M. B. Piccoli, A. J. Schultz, T. K. Todorova, L. Gagliardi and G. S. Girolami, *Angew. Chem., Int. Ed.*, 2010, **49**, 3379.
- 64 E. A. Dolgoplova, A. M. Rice and N. B. Shustova, *Chem. Commun.*, 2018, **54**, 6472.
- 65 C. Falaise, A. Assen, I. Mihalcea, C. Volkringer, A. Mesbah, N. Dacheux and T. Loiseau, *Dalton Trans.*, 2015, **44**, 2639.
- 66 V. Bon, I. Senkovska, D. Wallacher, D. M. Töbrens, I. Zizak, R. Feyerherm, U. Mueller and S. Kaskel, *Inorg. Chem.*, 2014, **53**, 1513.
- 67 C. Mellot-Draznieks, C. Serre, S. Surblé, N. Audebrand and G. Férey, *J. Am. Chem. Soc.*, 2005, **127**, 16273.
- 68 M. K. Taylor, T. Runčevski, J. Oktawiec, M. I. Gonzalez, R. L. Siegelman, J. A. Mason, J. Ye, C. M. Brown and J. R. Long, *J. Am. Chem. Soc.*, 2016, **138**, 15019.
- 69 P. Bénard and R. Chahine, *Langmuir*, 2001, **17**, 1950.
- 70 L. J. Murray, M. Dincă and J. R. Long, *Chem. Soc. Rev.*, 2009, **38**, 1294.
- 71 F. M. Mulder, B. Assfour, J. Huot, T. J. Dingemans, M. Wagemaker and A. J. Ramirez-Cuesta, *J. Phys. Chem. C*, 2010, **114**, 10648.
- 72 F. Salles, D. I. Kolokolov, H. Jovic, G. Maurin, P. L. Llewellyn, T. Devic, C. Serre and G. Férey, *J. Phys. Chem. C*, 2009, **113**, 7802.
- 73 R. A. Pollock, J.-H. Her, C. M. Brown, Y. Liu and A. Dailly, *J. Phys. Chem. C*, 2014, **118**, 18197.
- 74 H. Wu, W. Zhou and T. Yildirim, *J. Am. Chem. Soc.*, 2007, **129**, 5314.
- 75 D. Gygi, E. D. Bloch, J. A. Mason, M. R. Hudson, M. I. Gonzalez, R. L. Siegelman, T. A. Darwish, W. L. Queen, C. M. Brown and J. R. Long, *Chem. Mater.*, 2016, **28**, 1128.
- 76 K. Sumida, J.-H. Her, M. Dincă, L. J. Murray, J. M. Schloss, C. J. Pierce, B. A. Thompson, S. A. FitzGerald, C. M. Brown and J. R. Long, *J. Phys. Chem. C*, 2011, **115**, 8414.
- 77 T. Runčevski, M. T. Kapelewski, R. M. Torres-Gavosto, J. D. Tarver, C. M. Brown and J. R. Long, *Chem. Commun.*, 2016, **52**, 8251.
- 78 J. Luo, H. Xu, Y. Liu, Y. Zhao, L. L. Daemen, C. Brown, T. V. Timofeeva, S. Ma and H.-C. Zhou, *J. Am. Chem. Soc.*, 2008, **130**, 9626.
- 79 J. van Kranendonk and H. P. Gush, *Phys. Lett.*, 1962, **1**, 22.
- 80 V. K. Peterson, Y. Liu, C. M. Brown and C. J. Kepert, *J. Am. Chem. Soc.*, 2006, **128**, 15578.
- 81 S. Tsuzuki, K. Honda, T. Uchamaru, M. Mikami and K. Tanabe, *J. Am. Chem. Soc.*, 2000, **122**, 3746.
- 82 A. L. Ringer, M. S. Figgs, M. O. Sinnokrot and C. D. Sherrill, *J. Phys. Chem. A*, 2006, **110**, 10822.
- 83 H. Wu, W. Zhou and T. Yildirim, *J. Phys. Chem. C*, 2009, **113**, 3029.
- 84 E. Tsivion and M. Head-Gordon, *J. Phys. Chem. C*, 2017, **121**, 12091.
- 85 S. Tsuzuki, T. Uchamaru and K. Tanabe, *Chem. Phys. Lett.*, 1998, **287**, 202.
- 86 J. E. ten Elshof, C. R. Abadal, J. Sekulić, S. R. Chowdhury and D. H. A. Blank, *Microporous Mesoporous Mater.*, 2003, **65**, 197.

