

Cite this: *Sustainable Energy Fuels*,
2024, 8, 2751

Sheet-like ZnCo₂O₄ microspheres and pomelo peel waste-derived activated carbon for high performance solid state asymmetric supercapacitors†

Kiran Kumar Reddy Reddygunta,^a Lidija Šiller^b and Aruna Ivaturi^{a*}

A novel asymmetric supercapacitor based on zinc cobalt oxide (ZnCo₂O₄) as a positive electrode and pomelo peel-based activated carbon (PPAC-4) as a negative electrode was fabricated. ZnCo₂O₄ was synthesized using hydrothermal method and shows a distinct sheet-like structure clubbed together to form microspheres. PPAC-4 was synthesized via the chemical activation of pomelo peel hydrochar using KHCO₃ as the activation agent. The as-prepared ZnCo₂O₄ microspheres displayed maximum specific capacitance of 422 F g⁻¹ at an applied current density of 1 A g⁻¹, whereas PPAC-4 demonstrated a capacitance of 356 F g⁻¹ at a current density of 1 A g⁻¹. Moreover, the novel ZnCo₂O₄//PPAC-4 asymmetric solid-state supercapacitor with hydroxyethyl cellulose/potassium hydroxide (HEC/KOH) gel electrolyte displayed maximum operating voltage of 1.6 V with a superior energy density of 29.8 W h kg⁻¹ at a power density of 796.3 W kg⁻¹. Besides, a long-term cycling stability of 83% was achieved after 10 000 charge/discharge cycles, indicating its promise for future energy storage applications.

Received 4th February 2024
Accepted 13th May 2024

DOI: 10.1039/d4se00182f

rsc.li/sustainable-energy

Introduction

Supercapacitors have drawn considerable interest because of their ability to instantly offer more power and energy densities that lie between those of traditional batteries and dielectric capacitors, along with prolonged lifespan.^{1,2} Electric double-layer capacitors (EDLCs) and faradaic pseudocapacitors are further subcategories of supercapacitors based on their charge storing mechanism. EDLCs store charge via electrostatic adsorption/desorption of electrolyte ions at the electrode/electrolyte junction. Carbonaceous materials such as activated carbon, carbon nanotubes, and graphene are the preferred electroactive materials for EDLCs owing to their unique characteristics such as large specific surface area (SSA), superior electrical conductivity and good electrochemical stability. However, EDLCs deliver extremely low capacitance and energy densities, which impede their commercial applications. Conversely, a great deal of research has been conducted on pseudocapacitive materials as substitute electrode materials for supercapacitors to increase their energy densities. These materials include conducting polymers and transition metal derivatives with highly reversible redox reactions across the

electrode/electrolyte interface. However, pseudocapacitive materials show some shortcomings such as low conductivity, limited power densities and poor cycling stability.^{3,4} Coupling the positive effects of EDLCs and pseudocapacitive electrodes in a single unit results in an asymmetric supercapacitor, where charge storage takes place due to both electrostatic and redox reactions. As a result, fabricating an asymmetric supercapacitor that uses carbonaceous materials as negative electrodes and pseudocapacitive materials as positive electrodes yields a better voltage window, taking advantage of both the faradaic redox-type behavior and EDLCs significantly enhancing the energy density.^{5,6}

On account of its exceptional structural and electrochemical characteristics, such as large SSA, interconnected porous architecture, high conductivity, and excellent electrochemical stability, biomass activated carbon (AC) is an ideal negative electrode material for constructing asymmetric supercapacitors.⁷ Moreover, the production of activated carbon from biomass has various benefits, including the possibility for industrial scale production, renewability, abundance, and environmental friendliness. Several types of agricultural wastes have been utilized as renewable precursors for the production of porous carbons for use in supercapacitors.⁸ Pomelo, a citrus fruit available in almost every corner of the world, is rich in nutrients and has high medicinal value. However, its peels are largely discarded as waste, though they can be used as a renewable source for synthesizing large surface area activated carbon. Numerous studies have been published on the use of

^aSmart Materials Research and Device Technology (SMaRDT) Group, Department of Pure and Applied Chemistry, University of Strathclyde, Thomas Graham Building, Glasgow, G1 1XL, UK. E-mail: aruna.ivaturi@strath.ac.uk

^bSchool of Engineering, Newcastle University, Newcastle upon Tyne, NE1 7RU, UK

† Electronic supplementary information (ESI) available: Additional figures related to XRD, BET, Raman and XPS. See DOI: <https://doi.org/10.1039/d4se00182f>



porous carbon materials derived from pomelo peel waste as electrodes in supercapacitors. For instance, Liang *et al.*⁹ produced honeycomb like activated carbon (HLPC), which possessed a SSA of $2725 \text{ m}^2 \text{ g}^{-1}$ and displayed a specific capacitance of 342 F g^{-1} at 0.2 A g^{-1} . Furthermore, in 6 M KOH electrolyte, the HLPC electrode-based symmetric supercapacitor exhibited an energy density of 9.4 W h kg^{-1} . Peng *et al.*¹⁰ fabricated a symmetric supercapacitor with high SSA ($2105 \text{ m}^2 \text{ g}^{-1}$) pomelo peel-derived carbon electrodes and 1 M NaNO_3 aqueous electrolyte, which displayed an energy and power density of 17.1 W h kg^{-1} and 420 W kg^{-1} , respectively. In other instances, Wang *et al.*¹¹ fabricated dual-doped activated carbon from pomelo peels with nitrogen (N) and phosphorous (P), which exhibited an energy density of 11.7 W h kg^{-1} at 160 W h kg^{-1} when tested as a symmetric supercapacitor electrode in $1 \text{ M Na}_2\text{SO}_4$ aqueous electrolyte. Similarly, N,S-doped sponge-like activated carbon (NSC-600) was produced from pomelo peels, which showed a SSA of $1193 \text{ m}^2 \text{ g}^{-1}$ and capacitance of 310 F g^{-1} at 0.5 A g^{-1} current density in 6 M KOH electrolyte. Moreover, the assembled symmetric supercapacitor with NCS-600 electrodes and PVA/ H_2SO_4 electrolyte showed high energy and power density of 21.4 W h kg^{-1} and 2600 W kg^{-1} . However, the previously cited research demonstrated the fabrication of symmetric supercapacitors using porous carbon generated from pomelo peels waste and aqueous/synthetic polymer gel electrolytes. As far as we are aware, there is only one published work on the utilization of pomelo peel activated carbon as a negative electrode in an asymmetric supercapacitor. Qu *et al.*¹² synthesized N-doped carbon (PFNC) with high SSA ($1648.6 \text{ m}^2 \text{ g}^{-1}$), which displayed a specific capacitance of 260 F g^{-1} in 2 M KOH electrolyte at 1 A g^{-1} . Furthermore, the assembled asymmetric supercapacitor with porous nickel oxide (PFN)-based positive electrode and PFNC negative electrode displayed an energy density of $27.75 \text{ W h kg}^{-1}$ at 300 W kg^{-1} power density in 2 M KOH electrolyte. Although the asymmetric supercapacitor discussed above showed excellent charge storage performance, the device was evaluated in an aqueous electrolyte system, which may not be suitable for practical application. Thus, in the present work, high SSA activated carbon has been produced from pomelo peel wastes and utilized as a negative electrode to prepare an asymmetric supercapacitor with HEC/KOH gel electrolyte.

Binary metal oxides such as cobalt molybdenum oxide (CoMoO_4),^{13,14} copper cobalt oxide (CuCo_2O_4),^{15,16} nickel cobalt oxide (NiCo_2O_4),^{17,18} and zinc cobalt oxide (ZnCo_2O_4)^{19,20} have been explored as novel pseudocapacitive electrodes in the past decade. These binary transition metal oxides are composed of one or more electrochemically active/inactive ions and at least one transition metal ion. Because binary metal oxides include multivalent oxidation states for several metal cations, they perform exceptionally well in terms of capacitance when compared to single metal oxide materials.^{21,22} Among them, ZnCo_2O_4 has a maximum theoretical specific capacitance of 2604 F g^{-1} as well as multiple valence states that allow a variety of reversible redox reactions, which in turn leads to high energy storage performance. Rajesh *et al.*²⁰ prepared coral-like ZnCo_2O_4 nanostructures, which showed a specific capacity of

694 F g^{-1} at 2 A g^{-1} current density in 2 M KOH electrolyte. Chen *et al.*¹⁹ also reported mesoporous ZnCo_2O_4 microspheres, which exhibited a specific capacitance of 689 F g^{-1} at 1 A g^{-1} current density. To the best of our knowledge, there have been very few studies on employing ZnCo_2O_4 as a positive electrode for asymmetric supercapacitors. Chen *et al.*²³ fabricated asymmetric supercapacitors utilizing activated carbon as the negative electrode and ZnCo_2O_4 quasi cubes as the positive electrode. The fabricated supercapacitor achieved an energy density of 34.4 W h kg^{-1} at a power density of 860.1 W kg^{-1} in 2 M KOH electrolyte and retained 79.2% of its capacitance after 3000 charge/discharge cycles at 5 A g^{-1} . Similarly, Zhu *et al.*²⁴ reported ZnCo_2O_4 and activated carbon-based asymmetric supercapacitor with excellent energy density of $36.31 \text{ W h kg}^{-1}$ in 2 M KOH aqueous electrolyte. However, in both the above-mentioned cases, the asymmetric supercapacitors were fabricated with aqueous electrolyte, which poses severe safety constraints (volatile when exposed to high temperatures and leakage problems) and limits their practical application. Hence, in the present work, zinc cobalt oxide (ZnCo_2O_4) and pomelo peel-derived porous carbon were employed as the positive and negative electrode to fabricate an asymmetric supercapacitor that delivers high energy and power density. The microsphere-like ZnCo_2O_4 sheets were prepared through the hydrothermal process, and the activated carbon was prepared by the hydrothermal carbonization and KHCO_3 activation of pomelo peel waste. Pomelo peel-derived activated carbon and ZnCo_2O_4 electrodes were successfully integrated into an asymmetric supercapacitor device, which exhibits superior electrochemical properties in hydroxyethyl cellulose/potassium hydroxide (HEC/KOH) electrolyte with 1.6 V working voltage, superior energy density of 29.8 W h kg^{-1} at a power density of 796.3 W kg^{-1} , along with excellent cyclic stability (83%) after 10 000 charge/discharge cycles. The current study shows that the synergistic pairing of pomelo peel-derived porous carbon and ZnCo_2O_4 nanostructures has the potential to improve supercapacitor performance while also providing a sustainable approach of utilising pomelo peel waste for energy storage.

Experimental section

Materials and reagents

Pomelo fruit was bought from a nearby store in Edinburgh, UK and used as a carbon source. The following materials were purchased from Sigma-Aldrich: potassium hydroxide (KOH), potassium bicarbonate (KHCO_3 , 99.7%), polyvinylidene fluoride (PVDF) binder, 1-methylpyrrolidone, hydroxyethyl cellulose (HEC), zinc nitrate hexahydrate [$\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, 99%], cobalt nitrate hexahydrate [$\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, 98%], and urea [$\text{CH}_4\text{N}_2\text{O}$]. Hydrochloric acid (HCl, 37%) was procured from Fisher Scientific.

Synthesis of activated carbon from pomelo peels (PPAC-N)

For the preparation of activated carbon from pomelo peels, a pre-hydrothermal treatment followed by chemical activation was followed. 3 g of dried pomelo peel waste was cut into small



For a two-electrode device, the total capacitance C_t ($F\ g^{-1}$), energy density E_d ($W\ h\ kg^{-1}$) and power density P_d ($W\ kg^{-1}$) were measured from the GCD curves by means of eqn (2)–(5)^{27,28}

$$C_t = \frac{I}{M \left(\frac{\Delta V}{\Delta t} \right)} \quad (2)$$

$$E_d = \frac{1}{2} \frac{C_t \times \Delta V^2}{3.6} \quad (3)$$

$$P_d = \frac{E_d \times 3600}{\Delta t} \quad (4)$$

where $(\Delta V/\Delta t)$ is the area under the discharge curve and M is the total weight of the active material in the two electrodes.

For the construction of an asymmetric supercapacitor, the charge balance will follow the relationship $q^+ = q^-$. The specific capacitance (C_s), potential range for the charge/discharge process (ΔV), and electrode mass (m) determine the amount of charge held by each electrode, as indicated in eqn (5).^{29,30}

$$q = C_s \times \Delta V \times m \quad (5)$$

In order to get $q^+ = q^-$, the mass balancing will follow eqn (6).

$$m^+ / m^- = C_{s-} \times \Delta V^- / C_{s+} \times V^+ \quad (6)$$

The mass ratio of $m(\text{ZnCo}_2\text{O}_4)/m(\text{PPAC-4})$ was estimated to be 1.46 from the specific capacitance calculated from their GCD curves.

Results and discussions

XRD studies

The crystalline phase and microstructure of the PPAC- N and ZnCo_2O_4 samples were studied using X-ray diffraction measurements. The XRD patterns of all PPAC- N materials were identical, as shown in Fig. 1(a) and S1(a),† with peaks at $2\theta = 26.1^\circ$ and 44.2° corresponding to the (002) and (100) planes, respectively, of amorphous carbon structures with partially graphitic nature.^{2,31} The high intensity in the low angle region could potentially be attributed to the micropores found in PPAC- N .³² A close analysis reveals the existence of a broad peak at 23° , which can be ascribed to the (100) plane of graphitic carbon found in amorphous carbon structures.³³

Fig. 1(b) XRD pattern of the ZnCo_2O_4 sample. The diffraction peaks at $2\theta = 19.3^\circ, 31.7^\circ, 36.8^\circ, 38.5^\circ, 44.9^\circ, 55.7^\circ, 59.5^\circ, 65.4^\circ,$

$74.1^\circ,$ and 77.4° were indexed to the (111), (220), (311), (222), (400), (422), (511), (440), (620), and (533) planes of cubic spinel ZnCo_2O_4 .^{19,20} Furthermore, no additional peaks confirm the purity of the synthesized materials.

N_2 adsorption/desorption studies

The N_2 adsorption/desorption isotherms of the PPAC- N samples shown in Fig. 2(a) and S2(a)† can be classified as type IV isotherms according to the IUPAC classification.^{2,34} The isotherms demonstrate a steep uptake tendency at low relative pressure ($P/P_0 < 0.4$), which specifies the presence of micropores in all the samples. All the samples display an H4 type hysteresis loop, indicating the hierarchical porous structure with the co-existence of micro and mesopores in the carbon structure. Furthermore, the presence of macropores is indicated by the increased tail at the relatively high pressure range between 0.95 and 1.0 (P/P_0) in all the samples.^{35,36} From Table S1 (ESI),† the SSA and pore volume increased from 855 to $2089\ \text{m}^2\ \text{g}^{-1}$ and from 0.47 to $1.28\ \text{cm}^3\ \text{g}^{-1}$, respectively, as the concentration of the activating agent KHCO_3 increased from $1\ \text{M}$ to $4\ \text{M}$. Further increasing the concentration ($>4\ \text{M}\ \text{KHCO}_3$) resulted in a decrease in both the SSA and pore volume to $1530\ \text{m}^2\ \text{g}^{-1}$ and $0.97\ \text{cm}^3\ \text{g}^{-1}$, respectively. According to these findings, an increase in the concentration of KHCO_3 from 1 to $4\ \text{M}$ contributes to the formation of new pores as well as enlargement of existing ones, leading to an increase in the SSA and pore volume. However, we believe that higher KHCO_3 concentration ($>4\ \text{M}$) leads to the structural contraction and collapse of the pores, thereby reducing the SSA and pore volume. The pore size distribution (PSD) curve shown in the inset of Fig. 2(a) and S2(b)† indicates the existence of mesopores with an average pore size of $3.9\ \text{nm}$ and sizes ranging from 2 to $5\ \text{nm}$. From these results, it can be inferred that the PPAC-4 sample has a high SSA and pore volume, which can facilitate a significant accumulation of charge carriers and provide faster charge transport kinetics, thereby improving the supercapacitive performance of PPAC-4 in comparison to other activated carbons derived from pomelo peel.

The N_2 adsorption/desorption isotherms of ZnCo_2O_4 correspond to type-IV with H3 hysteresis loop [Fig. 2(b)], indicating the formation of a mesoporous structure.¹⁹ The ZnCo_2O_4 sample displays an SSA of $46\ \text{m}^2\ \text{g}^{-1}$, pore volume of $0.30\ \text{cm}^3\ \text{g}^{-1}$ and the sample mainly consists of mesopores with the pore

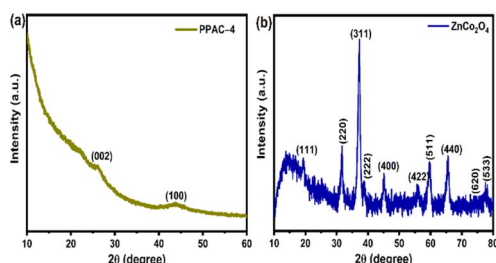


Fig. 1 XRD patterns of (a) PPAC-4 and (b) ZnCo_2O_4 samples.

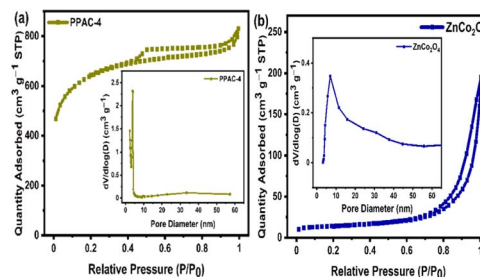


Fig. 2 N_2 adsorption/desorption isotherms, with the inset showing the pore size distribution plot of the (a) PPAC-4 and (b) ZnCo_2O_4 samples.



size mainly distributed between 5 and 30 nm, as indicated in the inset of Fig. 2(b) with an average pore size of 23.2 nm. The presence of mesopores in the as-prepared ZnCo_2O_4 often improves the interfacial electrode/electrolyte contact, accelerates the electrolyte ion diffusion and hence, superior pseudocapacitive performance can be achieved.^{19,24}

Raman studies

Fig. 3(a) and S3(a) [ESI†] presents the Raman spectra of all the pomelo peel-derived activated carbon (PPAC-*N*) samples. The as-prepared PPAC-*N* samples possess two strong peaks centered at $1340 \pm 5 \text{ cm}^{-1}$ and $1580 \pm 5 \text{ cm}^{-1}$, attributed to D bands (ascribed to the disordered carbon atoms) and G bands (attributed to the sp^2 -hybridized graphitic carbon atoms), respectively.³⁷ The Raman spectra of PPAC-*N* samples are further deconvoluted into four distinct peaks, as indicated in Fig. 3(b) and S3(b-e).† According to the literature, the peaks centered at about 1250, 1342, 1495, and 1580 cm^{-1} correspond to D4-band, D1-band, D3-band and G-band, respectively. In general, the D4-band corresponds to the polyene/oligomer, the D1-band arises from the disorder/defects in the lattice structure of the carbon materials, the D3-band represents the amorphous carbon and the G-band is attributed to the sp^2 hybridized graphitic carbons embedded in the porous carbon framework.^{2,38,39} The intensity ratio of the D1 and G band ($I_{\text{D1}}/I_{\text{G}}$) specifies the degree of graphitization of carbon materials.³⁸ The calculated $I_{\text{D1}}/I_{\text{G}}$ ratios of the as-prepared samples are in the order PPAC-4 (0.54) < PPAC-3 (0.58) < PPAC-2 (0.75) < PPAC-5 (0.83) < PPAC-1 (0.94), respectively. The PPAC-4 sample exhibited lowest $I_{\text{D1}}/I_{\text{G}}$ value, which corresponds to the highest degree of graphitization among all the pomelo peel-derived activated carbons. From the Raman and N_2 sorption analysis, it can be inferred that the PPAC-4 sample possesses a higher graphitization degree and high SSA, where the high SSA provides copious surface-active sites for the electrolyte ions to access, whereas the higher graphitization degree enhances the charge

transport kinetics and promotes the penetration of electrolyte ions deep into the carbon framework. Hence, the optimized PPAC-4 sample was utilized for electrochemical experiments because of its excellent textural characteristics compared to the other pomelo peel-derived activated carbons.

For the ZnCo_2O_4 sample, Raman peaks were observed at 471, 513, 602, and 665 cm^{-1} , which correspond to the E_{g} , $F_{2\text{g}}^{(2)}$, $F_{2\text{g}}^{(1)}$, and $A_{1\text{g}}$ modes, respectively, as shown in Fig. 3(c). The Raman E_{g} mode at 471 cm^{-1} is ascribed to the strong stretching vibrations of Co–O and Zn–O bonds in the as-prepared ZnCo_2O_4 sample. On the other hand, the $F_{2\text{g}}^{(2)}$, $F_{2\text{g}}^{(1)}$, and $A_{1\text{g}}$ modes at higher wavenumbers are attributed to the stretching vibration of the Co–O bond. Except for a slight shift in the peak position for a few peaks, all the peaks defined here indicate the formation of ZnCo_2O_4 , which are in accordance with the previous reports.^{19,23}

XPS analysis

The binding energy states of the PPAC-*N* and ZnCo_2O_4 samples analysed using XPS and the corresponding spectra are displayed in Fig. 4 and S4.† From the complete survey scan of the PPAC-*N* samples indicated in Fig. 4(a) and S4(a),† the peaks observed in the pomelo peel-derived activated carbons confirm the existence of carbon (C), oxygen (O) and nitrogen (N) in the survey spectrum, where these N and O groups are adsorbed on the surface of the porous carbon framework. The high-resolution C 1s, N 1s, and O 1s spectra of all the carbon samples are further deconvoluted into discrete peaks, as indicated in Fig. 4 (b–d) and S4(b–d)† to provide a deeper knowledge of individual elements in the as-prepared PPAC-*N* samples. The high-resolution C 1s spectra given in Fig. 4(b) and S4(b)† are split into three distinct peaks at 284.5 eV (C=C/C–C), related to the presence of graphitic carbon, 286.2 eV, belonging to C–O/C–N bonds, and 289.2 eV, related to the C=O bonds.^{40,41} On the other hand, the nitrogen (N 1s) present in the as-prepared carbon samples are split into three peaks with energy of about 398.2 eV, 400 eV, and 402.3 eV [indicated in Fig. 4(c) and S4(c)†], which correspond to the pyridinic-N, pyrrolic-N, and quaternary-N, respectively.^{40,41} Moreover, the high-resolution O 1s spectra given in Fig. 4(d) and S4(d)† are divided into two peaks at 531.6 (C=O) and 533.4 (C–O) eV.^{2,41} According to the literature, the pyrrolic-N groups can engage in the faradaic reactions, generating additional pseudocapacitance, whereas quaternary-N bonds along with the oxygen functionalities effectively increase the wettability of the electrode material by the electrolyte.^{42,43}

Fig. 4(e–h) demonstrates the composition and surface valence states of the as-prepared ZnCo_2O_4 sample. The survey scan of the ZnCo_2O_4 sample is shown in Fig. 4(e), which reveals the existence of zinc (Zn), cobalt (Co), oxygen (O), and small amount of carbon (C) in the as-prepared binary metal oxide sample. The high-resolution Zn 2p spectra in Fig. 4(f) consists of two prominent peaks at 1020 eV and 1043 eV, which are assigned to the Zn $2\text{p}_{3/2}$ and Zn $2\text{p}_{1/2}$ spin orbital states, demonstrating the Zn^{2+} oxidation state in the ZnCo_2O_4 sample. The Co 2p core level spectrum in Fig. 4(g) consists of two major

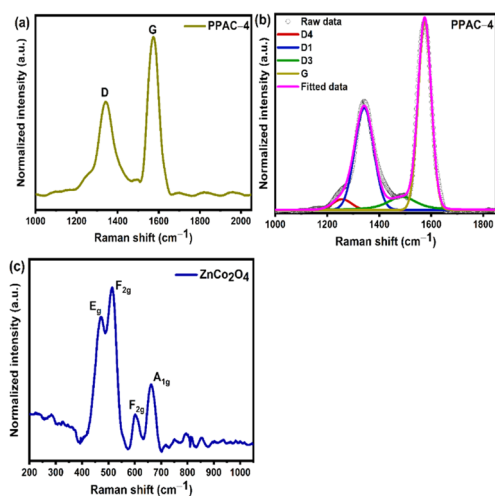


Fig. 3 (a) Raman spectra of the PPAC-4 sample. (b) Deconvoluted Raman spectra of the PPAC-4 sample. (c) Raman spectra of the ZnCo_2O_4 sample.



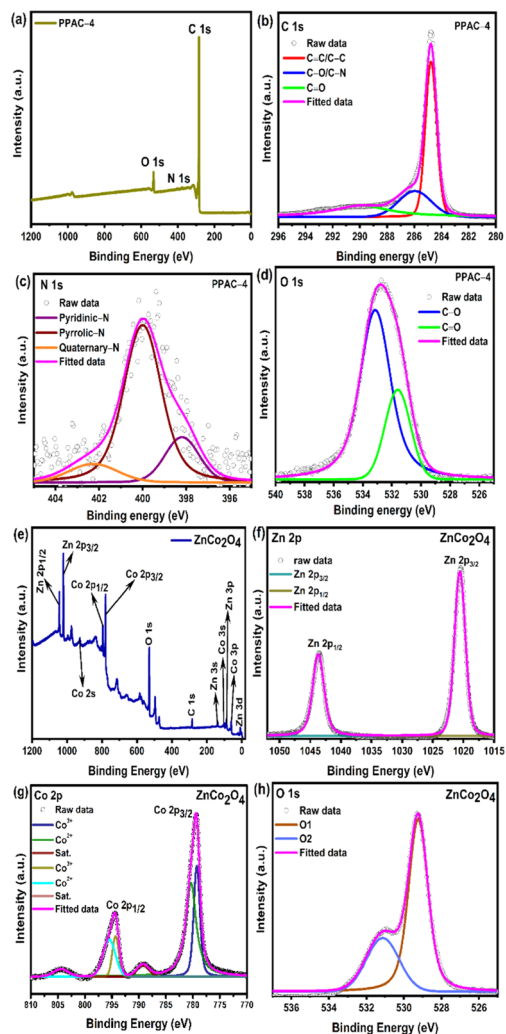


Fig. 4 XPS (a) full survey spectra of the PPAC-4 sample; high-resolution spectra of (b) C 1s, (c) N 1s and (d) O 1s peaks of the PPAC-4 sample. (e) Full survey spectra of ZnCo_2O_4 sample; high resolution spectra of the (f) Zn 2p, (g) Co 2p and (h) O 1s peaks of the ZnCo_2O_4 sample.

peaks with a peak spacing of ~ 15 eV centered at about 779 eV ($\text{Co } 2p_{3/2}$) and 794 ($\text{Co } 2p_{1/2}$) eV, indicating the formation of Co^{3+} species in the ZnCo_2O_4 sample. Following peak deconvolution, the Co^{3+} oxidation state in ZnCo_2O_4 was identified by two peaks at binding energies of 779.1 and 794.3 eV, and its Co^{2+} oxidation state by two more peaks at 780.4 and 795.6 eV. Additionally, the broad peaks at 788.5 eV and 802.4 eV are called the satellite peaks and they provide additional evidence that the sample possess the Co^{2+} oxidation state. The core level spectra of O 1s is deconvoluted into two peaks (as shown in Fig. 4(h)) centered at 529.2 (O 1) and 531.2 (O 2) eV. These O1 and O2 peaks represent the metal–oxygen bonds and the absorbed –OH molecules on the surface of the ZnCo_2O_4 sample, respectively.^{19,23,25} Based on the above analysis, we can deduce that Zn^{2+} and $\text{Co}^{2+}/\text{Co}^{3+}$ co-exist in ZnCo_2O_4 , which is in line with the results that have been previously published. The elemental composition (*i.e.*, the relative concentration of Zn, Co, O, and C

present in the samples) was calculated from the core energy levels of the individual elements using the peak areas.⁴⁴ The percentages of Zn, Co, O, and C were 13.7%, 31.2%, 51.3%, and 2.8%, respectively.

Morphological analysis

As indicated in Fig. 5(a and b), the field emission scanning electron microscopy (FESEM) images of the PPAC-4 sample reveal the presence of a hierarchical porous morphology containing disordered/uneven carbon structures with interconnected layered networks. These interconnected networks are particularly beneficial for the smooth and rapid transport of the electrolyte ions inside the porous carbon matrix and also helps in the complete utilization of the carbon surface during the electrochemical charge discharge process. Porous carbon along with the interconnected layered network are further confirmed with the HAADF-STEM imaging of the PPAC-4 sample shown in Fig. 5(c). The porous structure is beneficial for the accumulation of charge carriers whereas the interconnected layered network facilitates the faster transport of the ions and fully exposes the porous carbon matrix to the electrolyte ions. The energy-dispersive X-ray spectroscopy (EDX) elemental maps of the PPAC-4 sample [shown in Fig. 5(d–f)] obviously show the existence of C, N, and O elements, where the oxygen and nitrogen elements are randomly distributed on the surface of the porous carbon framework.

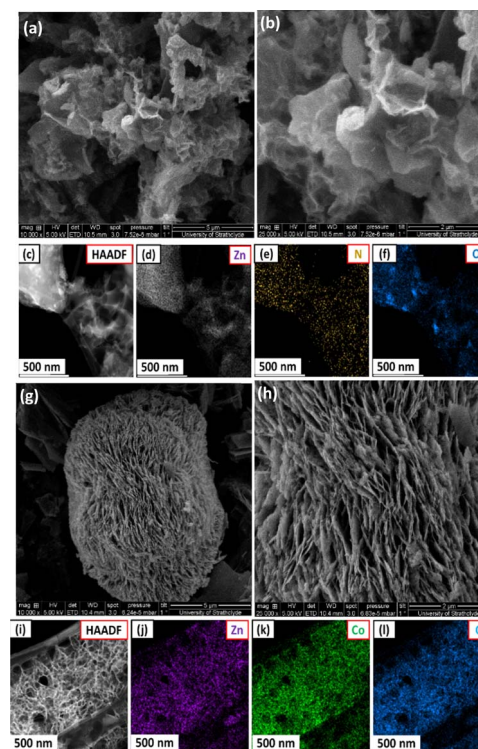


Fig. 5 (a and b) FESEM morphologies of the PPAC-4 sample at different magnifications. (c) HAADF image and (d–f) EDX elemental (C, N, and O) maps of the PPAC-4 sample. (g and h) FESEM morphologies of the ZnCo_2O_4 sample at different magnifications. (i) HAADF image and (j–l) EDX elemental (Zn, Co, and O) maps of the ZnCo_2O_4 sample.



The FESEM images of the ZnCo_2O_4 sample shown in Fig. 5(g) display the presence of spherical structures. A closer look at the FESEM image (Fig. 5(h)) reveals that the spherical ZnCo_2O_4 architectures are made up of several tightly interconnected porous nanosheets, which assembled to form microspheres. Notably, these nanosheets are in contact with one another, which may improve the mechanical strength and produce necessary openings for the rapid diffusion of electrolyte ions during the redox electrochemical activity, which is extremely useful for improving the electrochemical performance.¹⁹ The HAADF-STEM image of the ZnCo_2O_4 sample (shown in Fig. 5(i)) further confirms the existence of interconnected nanosheets. The elemental maps of the sheet like ZnCo_2O_4 microspheres are shown in Fig. 5(j–l), revealing the uniformly distributed O, Co, and Zn in the ZnCo_2O_4 sample.

Electrochemical performance of PPAC-4 and ZnCo_2O_4 electrodes measured in 2 M KOH electrolyte

The electrochemical performance of PPAC-4 and ZnCo_2O_4 electrodes were investigated in detail in the three-electrode configuration employing CV, GCD, and EIS techniques with 2 M KOH electrolyte. Fig. 6(a) and (c) show the electrochemical performance of PPAC-4 and ZnCo_2O_4 electrodes, which was examined across negative (−1 to 0 V) and positive (0 to 0.6 V) potential windows. Fig. 6(a) displays the PPAC-4 electrode's CV findings at various scan rates. The CV plot shows a quasi-rectangular shape with no redox peak, indicating the purity of the as-synthesized PPAC-4 electrode. This validates the characteristic EDLC nature of the PPAC-4 material. Similarly, the GCD plots in Fig. 6(b) yield a linear charge/discharge curve, confirming the double layer charge storage mechanism of the as-prepared carbon material. The CV measurements for the ZnCo_2O_4 sheet-like microspheres are performed between 5 and

100 mV s^{-1} scan rate within 0 to 0.6 V, as shown in Fig. 6(c). The form of the CV curves illustrated in Fig. 6(c) indicates that the ZnCo_2O_4 electrode has pseudocapacitive charge storage properties. The CV curves shown in Fig. 6(c) present a pair of redox reaction peak indicating the faradaic redox reactions, which might be related to the Co–O/Co–O–OH functional groups of ZnCo_2O_4 .^{19,23} The redox current response rises as the scan rate increases from 5 to 100 mV s^{-1} , suggesting that the sheet-like ZnCo_2O_4 microspheres have a quick redox reaction, strong electron conductivity, and rate capacity. Additionally, when the scan rate increases, the anodic and cathodic peaks move toward higher and lower potentials, respectively. This phenomenon may be related to the quasi-reversible nature of the anodic peaks and enhanced polarization at high scan rates.^{20,23} Fig. 6(d) displays the GCD plot of the ZnCo_2O_4 electrode. The nonlinear charge discharge curves at various current densities within the 0 to 0.6 V potential window further indicates the redox reactions in the electrode material and is in agreement with the CV curves shown in Fig. 6(c). Fig. 6(e) shows the effect of current density on the specific capacitance for both PPAC-4 and ZnCo_2O_4 electrodes. The ZnCo_2O_4 electrode showed a specific capacitance of 422 F g^{-1} at 1 A g^{-1} (specific capacity of 253 C g^{-1} at 1 A g^{-1} current density), which decreased to 328 F g^{-1} at 30 A g^{-1} current density, thus retaining $\sim 78\%$ of its starting capacitance. In the case of the PPAC-4 electrode, the specific capacitance was found to be 356 F g^{-1} at 1 A g^{-1} . Furthermore, the PPAC-4 electrode retained $\sim 70\%$ of its capacitance at 30 A g^{-1} current density. High specific capacitances are obtained at low current densities, which indicates higher interaction between the electrode and electrolyte ions. As the current density increases, the capacitance steadily decreases, which is most likely caused by the low diffusion of electrolyte ions (owing to less reaction time) or less number of active sites participating in redox processes at high current densities. The performance of the PPAC-4 and

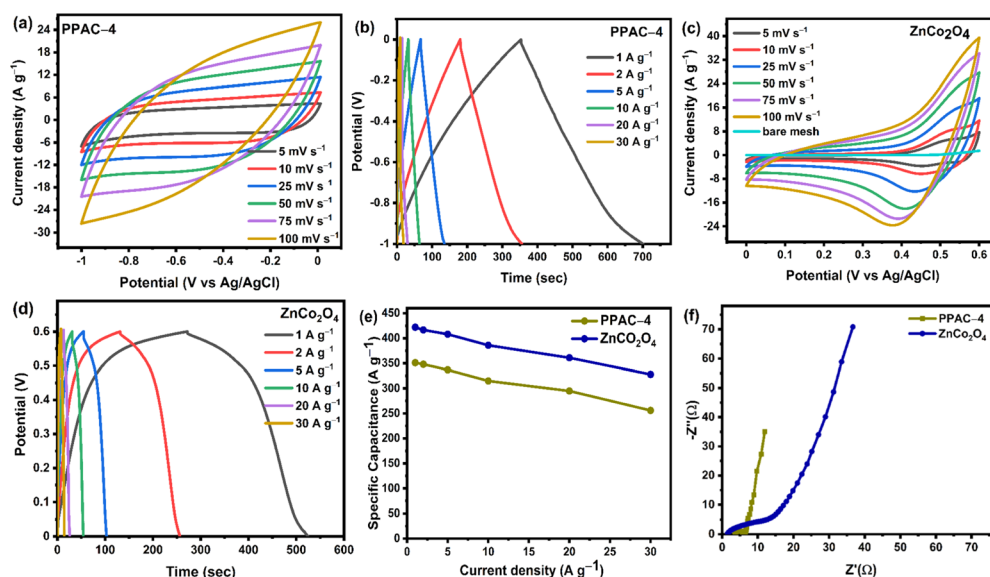


Fig. 6 (a) CV curves of the PPAC-4 electrode at different scan rates. (b) GCD curves of the PPAC-4 electrode at various current densities. (c) CV curves of the ZnCo_2O_4 electrode at different scan rates. (d) GCD curves of the ZnCo_2O_4 electrode at various current densities. (e) The specific capacitance versus current density for the PPAC-4 and ZnCo_2O_4 electrodes. (f) Nyquist plots of the PPAC-4 and ZnCo_2O_4 electrodes.



ZnCo₂O₄ electrodes was further investigated using EIS, and the corresponding Nyquist curve and equivalent circuit model are displayed in Fig. 6(f), S5a and b,[†] respectively. In the low frequency area, the PPAC-4 electrode exhibits a nearly vertical line, indicating almost ideal capacitive behaviour. In the high frequency zone, a semi-circle reveals the charge transfer resistance (R_{ct}). In the same low frequency range, the ZnCo₂O₄ electrode shows a more slanted curve, which suggests that pseudocapacitance is mostly responsible. After fitting the equivalent circuit model, the R_{ct} of PPAC-4 (2.62 Ω) was found to be less than that of the ZnCo₂O₄ (14.4 Ω) electrode. This is because ZnCo₂O₄ charge transfer includes slower redox processes than the simple surface adsorption/desorption that occurs in the PPAC-4 electrode. This is because of the presence of heteroatoms present in the PPAC-4 sample, which accelerates the charge transport kinetics inside the carbon matrix. The length of the Warburg line, or the slope of the 45° section in the mid frequency range, is particularly useful in expressing the ion diffusion process.⁴⁵ Since, the Warburg line of PPAC-4 is much shorter than that of ZnCo₂O₄, rapid ionic diffusion takes place in the porous interconnected carbon framework. The equivalent circuit model of PPAC-4 and ZnCo₂O₄ electrodes circuits is shown in Fig. S6(a and b) [ESI].[†] The components that make up the circuit model are Warburg impedance (W), constant phase element (Q), double-layer capacitance (C_{dl}), R_s , and R_{ct} . The ion transfer occurring inside the pores of the electrode is represented by the R_{ct} - C_{dl} circuit. The inclined line seen in the low-frequency area of the Nyquist plots illustrates the capacitive behaviour of the electrode denoted by Q in the equivalent circuit. From these findings, it can be concluded that the PPAC-4 electrode typically displays a EDLC mechanism whereas the ZnCo₂O₄ electrode stores the charge *via* the faradaic redox reactions.

Electrochemical performance of the asymmetric supercapacitor

The applicability of ZnCo₂O₄ and PPAC-4 was estimated using an asymmetric Swagelok supercapacitor cell with ZnCo₂O₄ as the positive electrode and PPAC-4 as the negative electrode with HEC-KOH biopolymer gel film as the electrolyte. The CV curves depicted in Fig. 7(a) indicate the capacitance involvement from both the electric double layer mechanism and pseudocapacitance mechanism at each scan rate. Moreover, significant redox peaks are visible even at high scan rates due to the strong pseudocapacitive nature of the ZnCo₂O₄ electrode. The shape of the CV curves remained stable even at 100 mV s⁻¹ scan rate, demonstrating the remarkable reversibility and rate capability of the supercapacitor. The GCD profiles of the ZnCo₂O₄//PPAC-4 supercapacitor at various current densities are displayed in Fig. 7(b). On the basis of the GCD curves, the specific capacitance of the device attained at 1 A g⁻¹ was 84 F g⁻¹, which reduced to 41 F g⁻¹ at 30 A g⁻¹. The drop in the specific capacitance at increased current density could be attributed to the limited ability of the ions to penetrate into the active material, resulting in a loss in specific capacitance. The prominent performance of this asymmetric supercapacitor can be

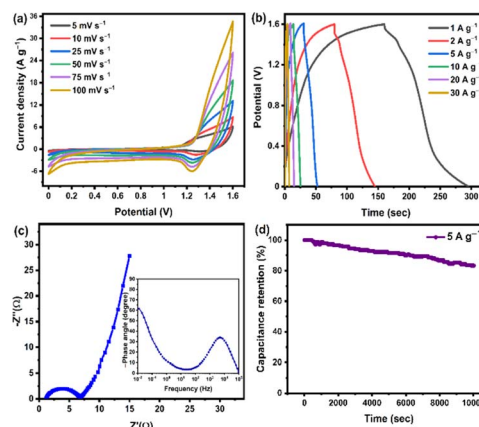


Fig. 7 (a) CV curves at different scan rates. (b) GCD curves at different current densities. (c) EIS plot with an equivalent circuit. (d) Long-term cycling stability tests of the ZnCo₂O₄//PPAC-4 asymmetric supercapacitor for 10 000 cycles performed at a current density of 5 A g⁻¹.

related to the combined effect between ZnCo₂O₄ microspheres and PPAC-4, where the high SSA of PPAC-4 provides bulk surface-active sites for the ions to access, while ZnCo₂O₄ provides high specific capacitance. To determine the resistance given by the asymmetric supercapacitor, EIS was performed, and the related Nyquist plot is presented in Fig. 7(c). The device exhibited a low series resistance of 1.15 Ω , which includes the resistance from the electrode, gel electrolyte film, and electrode/electrolyte interface.⁴⁶ The charge transfer resistance was observed to be 5.68 Ω , which is the resistance offered by electrode materials. The steep slope in the lower frequency area of the Nyquist plot may be attributed to the Warburg behaviour, which results from the fast diffusion of electrolyte ions across the electrode/electrolyte interface. The inset of Fig. 7(c) shows the Bode plot of phase angle plotted against frequency for the fabricated asymmetric device. The phase angle of -61.6° at low frequency is indicative of both pseudocapacitance and double layer capacitance contribution. The Nyquist plot of asymmetric supercapacitor was fitted with the equivalent circuit model to analyze the mechanism of the charge transfer process. Fig. S7(a) [ESI][†] shows the equivalent circuit used for fitting and the first resistance represents the series resistance (R_s). The parallel combination of capacitance and resistance (Q , R_{ct}) in the first part indicates the formation of double layer and the second part (Q) represents the diffusion region. The final part (Z_W) represents the Warburg diffusion. Furthermore, the cyclic performance of the as-prepared asymmetric supercapacitor was examined by the repetitive charge/discharge measurements for 10 000 cycles. The ZnCo₂O₄//PPAC-4 asymmetric supercapacitor has a remarkable cyclic stability of 83% capacitance retention over 10 000 cycles at 5 A g⁻¹, as indicated in Fig. 7(d). Such a superior performance is mainly related to the pseudocapacitive nature of sheet-like ZnCo₂O₄ microspheres and large SSA (2089 m² g⁻¹) of PPAC-4, which facilitates quick ion transfer and bulk active sites for charge storage.

To evaluate the feasibility of the ZnCo₂O₄//PPAC-4 asymmetric supercapacitor for practical applications, the Ragone



plot based on the GCD curves is plotted and compared with the existing literature in Table 1 as well as in Fig. 8(a). The as-prepared asymmetric supercapacitor achieved a maximum energy density of 29.8 W h kg^{-1} at a power density of 796.3 W kg^{-1} , and the energy density was reduced to 14.5 W h kg^{-1} at a higher power density of 23.8 kW kg^{-1} . This electrochemical performance of our ZnCo_2O_4 //PPAC-4 asymmetric supercapacitor with bio-polymer gel electrolyte film outperforms many previously reported asymmetric devices with aqueous electrolytes, as indicated in Table 1.^{7,23,47–53} We believe the synergistic effect of the high SSA activated carbon (PPAC-4) and sheet-like ZnCo_2O_4 microspheres, where PPAC-4 provides rich active sites for charge storage and ZnCo_2O_4 provides abundant channels for electrolyte ion transfer with rich pseudocapacitance to the asymmetric device. However, the performance of our bio-polymer gel electrolyte film-based asymmetric

supercapacitor is still lower than some of the aqueous electrolyte-based devices, for example, ZnCo_2O_4 quasi cubes//AC (34.4 W h kg^{-1} at 860.1 W kg^{-1})²³ and NiCo_2O_4 -HLPBC//AC (30.7 W h kg^{-1} at 900 W kg^{-1}).⁴⁹ The realistic feasibility of the ZnCo_2O_4 //PPAC-4 asymmetric supercapacitor for practical applications was studied by connecting it to a small motor/fan. Fig. 8(b) shows the asymmetric device charged to 1.6 V using a power supply. After charging for 1 minute, the device terminals are connected to motor as the load. As shown in Fig. 8(c), the as-prepared asymmetric device is able to power up the motor (for more than 4 minutes, see the corresponding video in ESI†), demonstrating the profound performance of the device for practical applicability in energy storage applications.

Conclusion

In summary, asymmetric supercapacitors fabricated from pomelo peel waste-derived activated carbon (PPAC-4) and ZnCo_2O_4 nanostructures show great potential for developing sophisticated energy storage devices. Morphological analysis using SEM and TEM analyses show that PPAC-4 has disordered/uneven carbon structures with interconnected layered networks, while ZnCo_2O_4 reveals spherical structures with tightly interconnected nanosheets. In addition, the as-prepared sheet-like ZnCo_2O_4 microspheres as the positive electrode exhibit a high specific capacitance of 422 F g^{-1} at 1 A g^{-1} current density, whereas the specific capacitance of PPAC-4 is 356 F g^{-1} at 0.5 A g^{-1} in the three-electrode configuration. Furthermore, the fabricated ZnCo_2O_4 //PPAC-4 asymmetric supercapacitor with bio-polymer gel electrolyte displayed excellent electrochemical performance with superior energy density of 29.8 W h kg^{-1} at a power density of 796.3 W kg^{-1} . Also, the fabricated device retained 83% of its performance even after 10 000 repetitive cycles at 5 A g^{-1} current density. This work not only extends the application of pomelo peel waste to the electrochemical energy storage application (high value-added activated carbon as negative electrodes) but also demonstrates that ZnCo_2O_4 and PPAC-4 are suitable for an affordable, high-performance battery-type supercapacitor to meet the high power and energy needs.

Author contributions

RKKR designed, carried out and analysed the majority of the practical work, as well as written the manuscript draft. LŠ performed the XPS measurements and helped with data fitting. AI conceptualized, actively supervised and assisted in interpreting the results. AI and LŠ provided inputs to the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

AI gratefully acknowledges Scottish Funding Council (SFC) Global Challenges Research Fund (GCRF) and Strathclyde

Table 1 Energy density and power density of the ZnCo_2O_4 //PPAC-4 compared with other asymmetric supercapacitors reported in the literature

| Device | Energy density (W h kg^{-1}) | Power density (W kg^{-1}) | Ref. |
|--|---|--------------------------------------|-----------|
| ZnCo_2O_4 //AC | 20.3 | 855 | 48 |
| ZnCo_2O_4 //AC | 27.7 | 158.5 | 52 |
| NiCo_2S_4 -RSAC//RSAC | 24.5 | 700 | 50 |
| ZnCo_2O_4 //AC | 26.2 | 716 | 47 |
| NiCo_2O_4 -CSPC//CSPC | 23.9 | 1298 | 53 |
| CoMn_3O_8 //HBFC | 24.3 | 850 | 7 |
| ZnCo_2O_4 // ZnCo_2O_4 | 11.8 | 2504 | 51 |
| ZnCo_2O_4 //AC | 34.4 | 860.1 | 23 |
| NiCo_2O_4 -HLPBC//AC | 30.7 | 900 | 49 |
| ZnCo_2O_4 //PPAC-4 | 29.8 | 796.3 | This work |

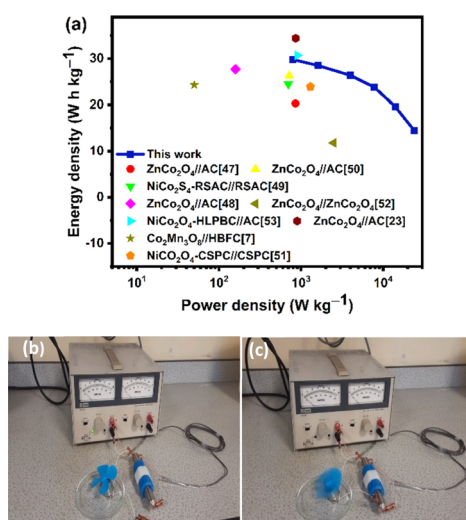


Fig. 8 (a) Ragone plot of the ZnCo_2O_4 //PPAC-4 asymmetric supercapacitor compared with other reported binary metal oxide//activated carbon asymmetric supercapacitor devices reported in the literature; practical application of the ZnCo_2O_4 //PPAC-4 asymmetric supercapacitor. (b) Device being charged at 1.6 V with power supply. (c) Performance of a motor/fan connected to the asymmetric supercapacitor.



- 48 L. Chen, Y. Jiao, Z. Li and Y. Gao, *Electrochim. Acta*, 2019, **299**, 388–394.
- 49 D. Guo, L. Zhang, X. Song, L. Tan, H. Ma, J. Jiao, D. Zhu and F. Li, *New J. Chem.*, 2018, **42**, 8478–8484.
- 50 R. Jiang, C. Zhou, Y. Yang, S. Zhu, S. Li, J. Zhou, W. Li and L. Ding, *Diamond Relat. Mater.*, 2023, 110322.
- 51 J. A. Rajesh, B.-K. Min, J.-H. Kim, H. Kim and K.-S. Ahn, *J. Electrochem. Soc.*, 2016, **163**, A2418.
- 52 Y. Shang, T. Xie, C. Ma, L. Su, Y. Gai, J. Liu and L. Gong, *Electrochim. Acta*, 2018, **286**, 103–113.
- 53 R. Wang, X. Li, Z. Nie, Y. Wang, Y. Zhao and H. Wang, *Energy Fuels*, 2022, **36**, 13256–13265.

