

RSC Applied Polymers

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. Dhiman, A. K. Sharma, R. Bartholomew, P. Bharti and G. Agrawal, *RSC Appl. Polym.*, 2026, DOI: 10.1039/D6LP00029K.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

The Rise of Polymeric Hydrogels, Sponges, and Electrospun Fibers as adsorbents for Microplastics Removal: Prospects for Sustainable Future

Ankita Dhiman,^{a,#} Amit Kumar Sharma,^{b,c,#} Bartholomew Richard,^a Priyanka Bharti,^a Garima Agrawal^{a,*}

^aSchool of Chemical Sciences and Advanced Materials Research Centre, Indian Institute of Technology Mandi, Mandi – 175075, Himachal Pradesh, India

^bDepartment of Chemistry, University Institute of Sciences, Chandigarh University, Mohali 140413, Punjab, India

^cUniversity Centre for Research & Development, Chandigarh University, Mohali 140413, Punjab, India

*Correspondence: garima@iitmandi.ac.in; Tel.: +91-1905267827; <https://orcid.org/0000-0002-3391-2378>

#Contributed equally to the manuscript.

Abstract

Microplastics (MPs) are ubiquitous and recognized as a significant environmental contaminant, owing to their persistent accumulation in terrestrial and aquatic environment. Microplastic pollution is primarily driven by rapid industrialization, improper disposal, and poor plastic waste management practices, and is extremely harmful to the environment and living species. To overcome this issue, sustainable approaches and mitigation strategies are necessary for removing MPs from environment. In this regard, various approaches have been developed so far including



adsorption which is considered highly efficient. So far, various types of adsorbents, including metal-organic frameworks (MOFs), inorganic nanoparticles-based composites, 2D nanomaterials, and polymeric materials have been explored for the removal of MPs. Among adsorption-based materials, polymeric hydrogels, sponges, and electrospun fibers have recently gained significant attention due to their high porosity, tunable surface properties, and excellent adsorption capacity. Additionally, biodegradable polymer-based materials offer the possibility of removing MPs without causing any adverse impact on the environment as they do not generate any toxic byproducts upon degradation after their purpose is served. However, several factors including material reusability, long-term stability, and capability to degrade MPs must be resolved for their better performance. Hence, in this review, we have comprehensively and critically highlighted the recent advancements in polymer-based hydrogels, sponges, and electrospun fibers for MPs removal. We also summarize the facts associated with the contamination caused by MPs and explore recent MPs removal techniques, including physical methods, chemical methods, and biological methods. In addition, we describe the management strategies that can help mitigating issues of MPs-based environmental pollution. Finally, we discuss the current challenges associated with these materials for facilitating MPs remediation in a more efficient, scalable, and environment-friendly way for sustainable future.

Keywords: Microplastics, Hydrogels, Electrospun fibers, Adsorption, Water purification, Sustainability.

1. Introduction

Plastic-based products are more convenient and used worldwide on mass scale for diverse applications including healthcare, agriculture, electronics, construction, transportation, and most



significantly packaging.¹ The journey of plastic began with the fabrication of first semisynthetic plastic *Xylonite*, which was produced by Alexander Parkes in 1861.² Following this, several plastics such as polyvinyl chloride (PVC), polyethylene terephthalate (PET), cellophane, polyamide (PA), and polyethylene (PE) were developed. They are extensively utilized because of their low cost, durability, versatility, ease of production, and ability to be moulded into various products that are integral to daily life.³

With exponentially growing population and rapid urbanization, the global plastic production has been reported to reach 359 million tons in 2018.⁴ This demonstrates a substantial leap of 1.2-fold from 299 million tons in the short time frame of 5 years.⁵ Despite several benefits, this rapid expansion of plastic utilization combined with inadequate handling and improper disposal of plastic waste has led to significant environmental accumulation causing detrimental effects.⁶ It has been anticipated that ~31.9 million metric tons of plastic waste is released into the environment every year due to poor waste management.⁷ Further, this plastic waste undergoes fragmentation via physical abrasion, chemical corrosion, and photooxidation, resulting in the formation of microplastics (MPs) ranging from 1 μm to 5 mm in size.⁸ MPs have been identified as one of the emerging pollutants in aquatic environment. It has been found that ~89% of the Northeast Atlantic Ocean, ~70% of Jade Bay South–North Sea, and ~95% of Arctic Polar water contains MPs which is a serious matter of concern.⁹

Based on their fabrication, MPs can be of two distinct types i.e., primary and secondary. Primary MPs are generally added into personal care products as microbeads.¹⁰ This also includes marine coatings, wear and tear of tyres, and microfibers coming from household laundry, and factories.¹¹ On the contrary, secondary MPs are generated by fragmentation of larger plastics via various processes, including physical degradation, biodegradation, photodegradation, oxidation,



and hydrolysis.¹²⁻¹³ They may also arise from the plastic waste of fishing, products abandoned during tourism, plastic products used in agriculture sector, and plastic garbage thrown away by residents during their daily life.¹⁴ MPs are more susceptible to be carried from soil to aquatic environment via runoff where they accumulate in sediments, and are further ingested by the aquatic organisms posing a significant threat to human health through the consumption of seafoods.¹⁵⁻¹⁶ It is to be noted that MPs are cytotoxic, and capable of inducing oxidative stress and inflammation that may disrupt vascular endothelial cells, and hamper immune and neurological functions in humans.¹⁷ They can enter the brain through the blood-brain barrier and can affect the discharge of essential neuroinflammatory transporters such as chemokine and cytokine.¹⁸ The MPs of size ≤ 20 μm can access the brain through blood vessels and lymphatics. The entry of MPs into the brain may destroy neurons and result in neural dysfunction. The adverse effects of MPs in the brain may be related to the pathogenesis of neurodegenerative disorders, including Parkinson's disease and Alzheimer's disease.¹⁹ Moreover, MPs can undergo aging process which alters their size,²⁰ surface area,²¹ hydrophilicity,²² color,²³ and thermal stability and crystallinity.²⁴ These transformations further enhance the concern of deeper infiltration of MPs in ecosystem.²⁵ Aged MPs have higher affinity to adsorb heavy metals,²⁶⁻²⁷ hydrophobic organic pollutants (e.g., pesticides, pharmaceuticals, polycyclic aromatic hydrocarbons) and polychlorinated biphenyls,²⁸ from water, which further increases their toxicity.

To combat the issue of MPs pollution, several methods have been explored so far including biological processes, membrane filtration, electrocoagulation, and chemical methods such as coagulation, flotation, and adsorption.²⁹⁻³⁰ The biological processes exhibit limited removal efficiency for MPs. Although membrane filtration offers a viable solution for capturing large sized MPs, yet its performance is limited for smaller MPs. These smaller MPs can easily clog the



membrane pores and hinder filtration process.²⁹ Chemical methods such as coagulation, flotation, and adsorption are more commonly employed owing to their simple operation, cost-effectiveness, and low energy consumption. However, the use of chemical reagents in water treatment makes coagulation and flotation less environment-friendly. On the contrary, adsorption is considered as most advantageous method for MPs removal owing to low cost, straightforward operation, and possible recyclability of adsorbents.³⁰ Previously, several adsorbent materials including layered double oxides, biochar, coffee grounds, and magnetic particles have been explored.³¹⁻³³ However, these materials tend to be ineffective against smaller MPs or nanoplastics (NPs), and often face limitations like poor efficacy, prolonged adsorption duration, and low reusability which hinders their large-scale implementation.^{27, 30} Compared to above-mentioned traditional adsorbents, the polymer-based materials possess interconnected porous architectures, tunable surface functionalities and pore size, improved hydrophilic/hydrophobic balance, enhanced mechanical flexibility, and large specific surface area that altogether enhances the capturing efficiency and reduces the fouling behaviour.³⁴⁻³⁵ The controlled pore size and tailored chemical functionalities also improve the interaction of such materials with MPs, and hence provide a multifunctional platform for designing next-generation separation techniques.

In the given scenario, polymeric hydrogels, sponges, and electrospun fibers-based adsorbents have emerged as a promising platform to remove MPs from ecosystem. In recent years, a few review articles have been published covering various types of adsorbents, including metal-organic frameworks (MOFs), metal nanoparticles-based composites, and 2D nanomaterials for the removal of MPs.^{30, 36-37} However, very limited attention has been given specifically to polymer-based adsorbents, including hydrogels, sponges, and electrospun fibers. Moreover, biodegradable polymer-based materials offer the possibility of removing MPs without creating any adverse



impact on the environment. Unlike engineered nanomaterials, covalent organic frameworks, and metal organic frameworks, these biocompatible and biodegradable polymer-based materials do not produce toxic by-products upon degradation. Usually, such polymeric materials offer the absorption of MPs through physical interactions such as electrostatic interactions, dipole-dipole interactions, hydrogen bonding, and π - π stacking interactions. Consequently, they are being widely explored as environmentally benign alternatives for microplastic remediation. Hence, a comprehensive review dedicated to these polymeric materials and their use for the removal of MPs can provide critical insights into their design, adsorption mechanisms, and practical applications, thereby guiding future research and development in this field.

Herein, we described the impact of MPs contamination and provided a comprehensive overview of current advances in polymeric hydrogels, sponges, and electrospun fibers-based membranes for eliminating MPs from water. Further, we discuss various management strategies that could help mitigating detrimental effect of MPs. Lastly, we highlight the key challenges associated with these materials and emphasize the need for continued research to improve their performance for MPs remediation on a large scale.

2. Background and motivation to control MPs pollution

The use of plastic-based products has significantly risen over the last 50 years. The annual production of plastic was 322 million tons in the year 2015 and is expected to reach 670 million tons in 2040.³⁸ It may be noted that instead of high production and rising demand of plastic-derived products, only 9-10% of the plastic waste has been recycled, and most of the waste is discharged into natural water resources that can be deposited in landfills.³⁹ The exact size of MPs is still not defined by the scientific community, and the MPs can show a maximum length of 5 mm in the



form of fibres, spheres, films, fragments and foams.⁴⁰⁻⁴¹ The shape of MPs depends upon their source of origin. For example, most of the fiber-shaped MPs are produced by the apparel industry, while film-shaped MPs are produced by packaging industry. Similarly, sphere-shaped MPs are generated by crushing media, waste generated by abrasives and resin pellet leakage from the transportation industry.⁴¹

It may be noted that the studies have shown that an individual absorbs 39,000 to 52,000 MPs every year.⁴² The microparticles can penetrate the gastrointestinal tract and can cause an inflammatory effect.⁴³ The chronic exposure to MPs can destroy the immune system and increase the risk of cancer. Moreover, smaller-sized MPs possess the potential for bioaccumulation and can exacerbate health issues (**Fig. 1**).⁴⁴⁻⁴⁵ Therefore, MPs removal from different sources is very crucial to safeguard our environment. Nowadays, different techniques, including physical, chemical, and biological methods, are being used to remove the MPs. This review mainly focuses on the advances of Polymeric Hydrogels, Sponges, and Electrospun Fibers for the removal of MPs.


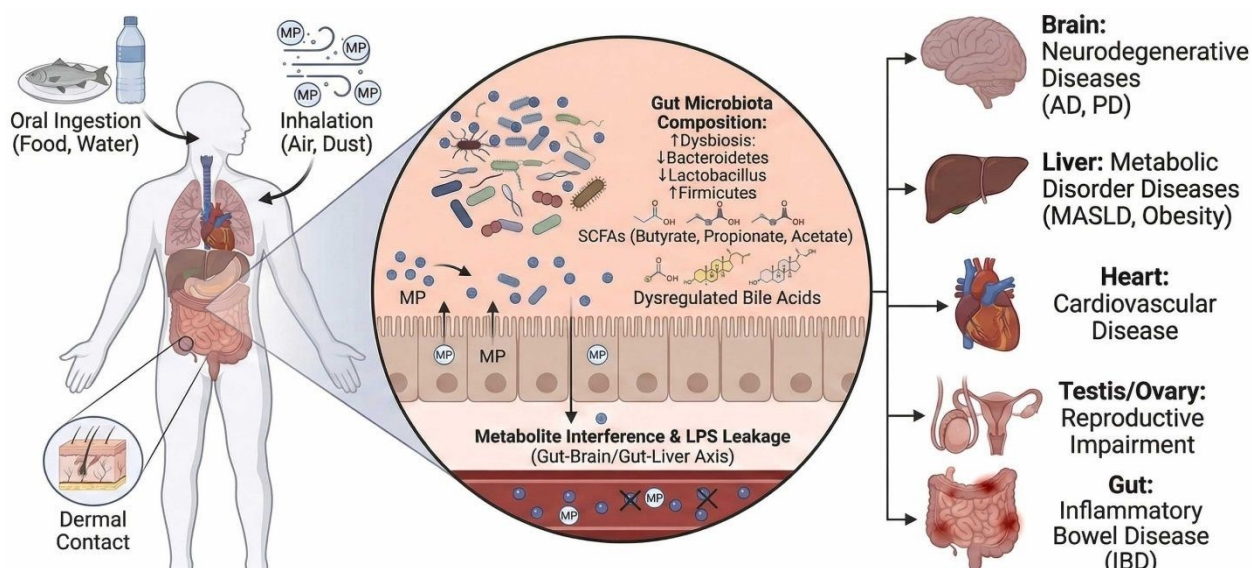


Fig. 1: Different pathways for human exposure to MPs and accumulation in distinct organs.

Adapted with permission.⁴⁵ Copyright 2026, Publisher Elsevier.



3. Adverse impact of contamination by MPs

Origin of MPs from different sources and their increasing amount in water has emerged as a critical problem, owing to their harmful effects on aquatic life and human health (**Fig. 2**). It has been reported that over 250 aquatic species are affected by the ingestion and exposure to MPs.⁴⁶ It is evidenced by the presence of MPs in their digestive tracts, which leads to abnormal growth, structural and physical damage, disruption of normal feeding habits, and suppression of innate immunity.⁴⁷ Eventually, the consumption of such seafood by humans results in accumulation of MPs in their body. This has been recently indicated by the findings suggesting the occurrence of MPs in human stool, tissues, and body fluids.⁴⁸⁻⁵² Long-term exposure of MPs can also cause skin irritation, cytotoxicity, neurotoxicity, reproductive complications, Alzheimer disease, and chronic inflammation which increases the risk of cancer.⁴⁷⁻⁴⁸ MPs can also affect cell metabolism in humans by altering the activity of gut microbiota, which reduces the absorption of nutrients in the gut.⁵³ Furthermore, MPs can also act as a vector for bacteria by providing substantial surface area for colony formation and proliferation.⁵⁴ This can result in tissue damage and increase the risk of infections.⁵⁴ Therefore, immediate intervention and development of novel technological alternatives is of prime importance for mitigating the issues related to MPs.



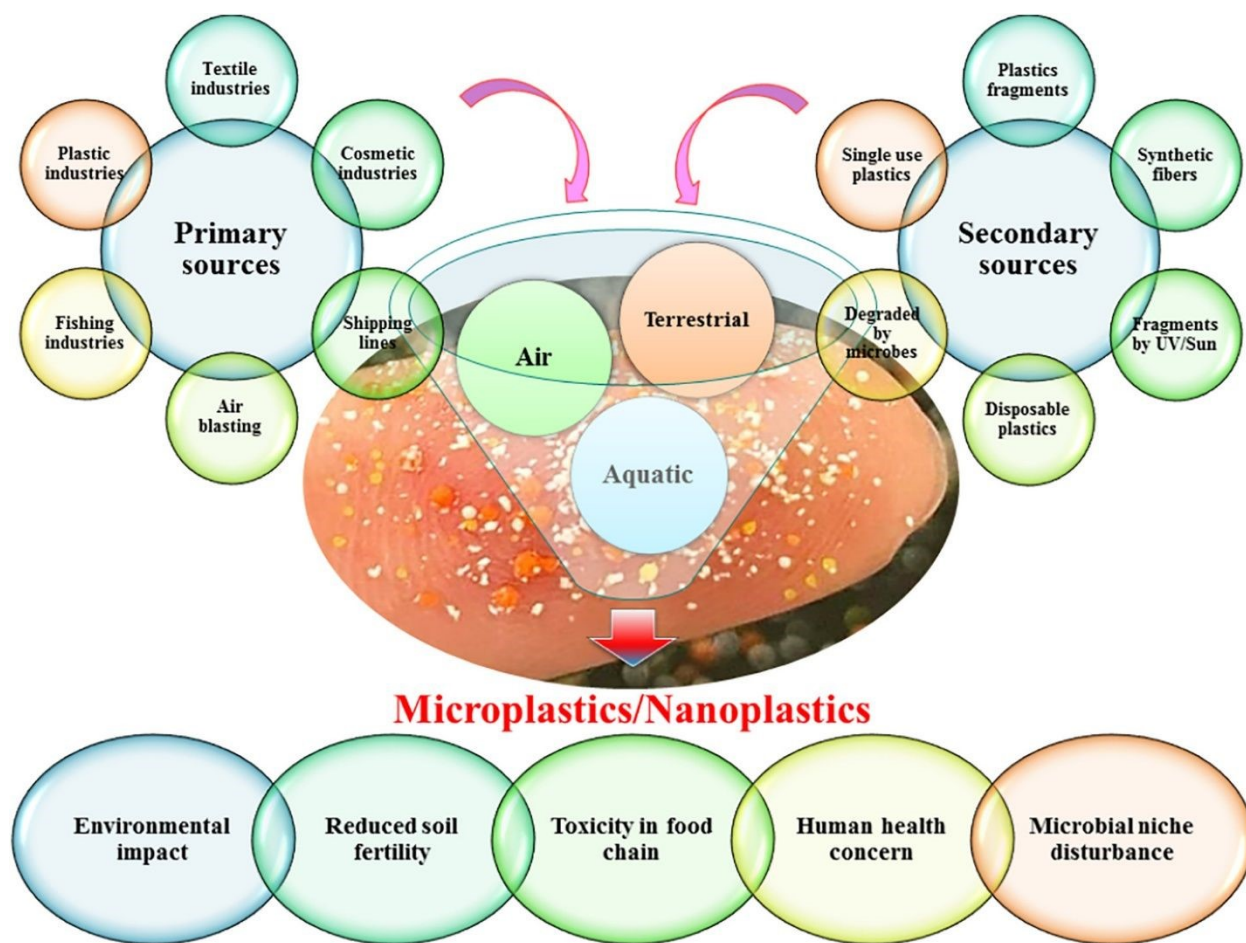


Fig. 2: Sources of MPs/NPs and their harmful impacts. Adapted with permission.⁴⁷ Copyright 2022, Publisher Elsevier.

4. Techniques for the removal of microplastics

In wastewater treatment plants, the most widely used methods may be physical, chemical, and biological methods. All these methods possess specific advantages as well as limitations for the recovery of microplastics from wastewater. A comparative analysis of these methods is summarized in **Table 1**.

4.1. Physical Methods



The physical methods employed for the removal of MPs usually retain the chemical and biological properties of MPs. The commonly employed physical methods may include magnetic separation, froth flotation, filtration, adsorption, the oil film method, etc.

Magnetic separation is an effective method for the removal of MPs that uses a variety of materials, including carbon nanotubes, iron nanoparticles and magnetic seeds. The major controlling factors for magnetic separation may include hydrogen bonding, electric friction and complexation. The separation of MPs is possible due to a variety of removal mechanisms, including electrostatic interactions, hydrophobic interactions, π - π interactions, hydrogen bonding and complexation. Once magnetized, MPs can be effectively separated from water using an external magnetic field. Shi *et al.* reported the synthesis of modified maifanite through high temperature and acid treatment for the effective removal of MPs using the magnetic separation method. The modified maifanite demonstrated 98.46% removal efficiency of polystyrene under the influence of rotating magnetic field and recyclable upto 25 operational cycles.⁵⁵

Similarly, the Froth flotation technique with ultrafine bubbles is an effective physical method for removing small MPs, including polylactic acid, polystyrene, polybutylene succinate, and polyethylene terephthalate from wastewater.⁵⁶ In this technique, there is selective adherence of bubbles to the required minerals, and the primary parameters required for froth flotation include surface wettability, hydrophilic interior, and hydrophobic outer surface tending to float in the form of froth aggregations.⁵⁷ A study carried out by Jiang *et al.* demonstrated that the efficacy of the froth flotation process for the removal of MPs can be enhanced by using cationic and anionic surfactants.⁵⁸

Filtration of MPs can be carried out either by using a sand filter, disc filter or biochar filters. The suspended materials such as MPs can be removed with the help of rapid sand filters that can



cling to the surface of sand grains. In wastewater treatment plants, A rapid sand filter may consist of a series of sand filters having distinct materials of different grain sizes. For example, Chabi *et al.* fabricated a rapid sand filter that can effectively remove MPs of size $< 10 \mu\text{m}$ with 98% removal efficiency and 97% desorption rate. The mechanism involved in this removal method was the synergic combination of physicochemical sorption.⁵⁹ Similarly, the disc filtration method is a frequently used method for the physical separation of MPs. In this method, the MPs removal is mainly dependent on the creation of cakes of sludge inside the filter panels as well as retention of particles in filters.⁶⁰ Disc filtration technique can achieve 98% efficiency for the removal of MPs as indicated by the reported study.⁶¹ However, the removal efficiency can vary depending upon the water quality, filter design, pore size and effectiveness of the disc filters. Biochar-based filters further enhance the removal efficiency of the filtration process. They consist of different media, including anthracite sand and granular activated carbon. Duan *et al.* designed an iron-modified magnetic biochar based on sawdust that depicted 205 mg/g adsorption capacity for the removal of polystyrene following Elovich kinetics and Sips isotherm model. The fabricated filter maintained 72% removal efficiency even after six cycles of pyrolysis.⁶² The oil film method is a hydrophobicity-based removal technique that is very effective for the removal of MPs. Wang *et al.* developed a superhydrophobic and multifunctional polyurethane sponge using polydimethylsiloxane (PDMS) and stearic acid-modified TiO_2 nanoparticles. The adsorption capacity of the material reaches 0.45 g/g within 10 s. In another study, magnetic cobalt ferrite particles were able to remove 100% of microplastics through the oil film method. The material also demonstrated 2.56 g/g capture capacity and 98% removal efficiency after 10 adsorption-desorption cycles.⁶³



Adsorption is the most favorable technique to remove MPs. A variety of adsorbent materials, such as iron oxide, graphene oxide, carbon nanotubes, etc., are being employed for the efficient removal of microplastics. For example, a study carried out by Heo *et al.* employed magnetic iron oxide nanoparticles demonstrating 98.2% adsorption efficiency for the removal of polystyrene MPs.⁶⁴ Similarly, reduced graphene oxide nanosheets were capable of removing 99.9 % of MPs through an adsorption process.⁶⁵ In short, the physical methods provide a reliable and non-destructive approach for the removal of MPs. The removal efficiencies can be enhanced by creating superhydrophobic–magnetic sponges, magnetic–biochar composites, and surface-engineered nanoparticles.⁶⁶ Out of these physical methods, adsorption is considered as the most versatile, cost-effective and highly efficient technique.

4.2. Chemical Methods

Chemical treatment methods are generally employed where the removal of MPs from wastewater is not possible with physical or biological treatment methods. The wastewater treatment using the chemical method may include a series of chemical reactions that help to selectively remove the MPs. Electrochemical oxidation, coagulation, flocculation, sol-gel techniques, photocatalytic degradation, and ozonization are frequently used chemical treatment methods for the removal of MPs.

Electrochemical oxidation is an affordable and sustainable method for the treatment of MPs present in wastewater. Instead of MP degradation, this method is suitable for the degradation of toxic dyes, organic pollutants, and medications. This method uses indirect cathode/anode oxidation and produces non-toxic degradation end products such as CO₂ and H₂O. Falco *et al.* demonstrated the fabrication of boron-doped diamond electrodes that can effectively remove 98.5% polystyrene



MPs from wastewater at 25 mgL⁻¹ initial MPs concentration, 90 min treatment time, and 8.07 mAcm⁻² current density at pH 4.⁶⁷ While the fabricated electrode showed high removal efficiency, the sludge generation during the removal process added operational cost related to the disposal of waste. In another study, the boron-doped diamond electrodes were also employed for the degradation of polyethylene terephthalate microplastics.⁶⁸ The removal efficiency was 81% in synthetic water and 95% in marine water with added salt due to the crucial role of chlorine species present in saline water. Moreover, the removal time was reduced from 12 h to 2h in saline water.

The coagulation/ flocculation method for the removal of MPs involves the neutralization of the charge present on the existing colloidal particles, which may form floccules and can be separated through sedimentation or filtration. For example, Zheng *et al.* employed polymeric ferric sulfate and Opuntia Milpa Alta particles for the removal of polystyrene MPs and achieved 93.6% removal efficiency at 20 mg/L Opuntia Milpa Alta concentration, 120 mg/L polymeric ferric sulfate concentration and 9.2 pH.⁶⁹ In comparison to chemical coagulation, the electrocoagulation method offers the use of metal electrodes, which is preferable over conventional coagulation techniques. For example, Sezer *et al.* suggested the optimization of the electrocoagulation method by Box Behnken Design and achieved 99% removal efficiency of MPs obtained from food packaging industry wastewaters under optimum conditions (i.e., current density: 3.16 mA cm⁻², pH: 6.74, and time: 13.58 min).⁷⁰

Ozonization is a tertiary treatment process used for the treatment of MPs present in the leftover residue of the coagulation process. The oxygen functionalities of the MPs can be degraded through ozonization. To improve the efficiency of ozonization, Hu *et al.* introduced 20 mM α -FeOOH into the ozonation system, and the mineralization efficiency in case of polyethylene MPs was found to be enhanced 3.27 folds due to the accelerated production of OH* free radicals.⁷¹ In



another study, the efficiency of ozonization was accelerated by implementing Co(II)-catalyzed ozonation. 1 mM Co^{2+} has reduced 20% turbidity of the wastewater and achieved 64% mineralization of MPs within 15 min of reaction time.⁷² The major drawback of ozonation process is its high operation cost. In addition, the incomplete ozonation process can produce intermediate components that can be toxic to the environment and can lead to the generation of reactive oxygen species.

Sol-gel technique is a chemical process that involves the agglomeration of organosilanes into an inorganic-organic macromolecule before its removal from wastewater.⁷³ Using the sol-gel method, Pacaphol *et al.* demonstrated the removal of small MPs such as polyethylene, polyethylene terephthalate, polystyrene, polyvinyl chloride, polytetrafluoroethylene, polypropylene, and aged tyre rubber. An excellent MPs recovery rate (95-100%) was observed using tetraethyl orthosilicate as a floating media. However, the recovery rates were slightly reduced (82-98%) for finer particles of sizes $< 40 \mu\text{m}$.⁷⁴

Photocatalysis is the most reliable and cost-effective chemical method for degrading toxic organic pollutants, including MPs. In this technique, the oxidation of MPs is carried out with the help of free radicals and reactive oxygen species produced by the semiconductor material while interacting with ultraviolet or visible light. Yang *et al.* prepared core-shell $\text{BiO}_{2-x}/\text{CuBi}_2\text{O}_4$ heterojunction for the effective degradation of polystyrene MPs. The results indicated that the complete surface of polystyrene was degraded in 30 days using the synthesized photocatalyst.⁷⁵ In another study, the photocatalytic degradation of micro polyethylene bags was studied using a ZnO-based photocatalysis-persulfate activation system. Hydroxyl and sulfate radicals were the major reactive species in the photocatalysis process, leading to a 50.91% mass loss ratio within 105 h.



The photocatalyst was recyclable up to many cycles, and the difference in the mass loss ratio of the first and fifth cycle was only 1%.⁷⁶

4.3. Biological Methods


Biological methods of MPs degradation include the treatment of wastewater with different bacterial isolates. The extent of MPs degradation depends upon the type of microplastic and bacterial strain. In comparison to physical and chemical degradation methods, the biological methods of MPs degradation are rarely used. However, some studies have suggested the use of bioreactors and dynamic membrane techniques to remove low-density microplastic sources.⁷⁷ For example, the studies carried out by Corpuz *et al.* showed a 95% reduction of polyethylene MPs using an electrochemically enhanced living membrane bioreactor. Moreover, the live membrane bioreactor mitigated the inhibition effect of MPs to PO₄-P and NH₄-N removals.⁷⁸ Lv *et al.* have shown the degradation of polystyrene MPs with *Alcanivorax xenomutans* and *Halomonas titanicae* marine bacteria. It was observed that only 4.5% and 1.9% of the plastic films were actually biomineralized with *A. xenomutans* and *H. titanicae* after 30 days of incubation.⁷⁹ In another study, *P. aeruginosa* and *S. haemolyticus* were isolated from landfill leachate that had shown the degradation of Polypropylene MPs. The maximum degradation efficiency achieved was 25.46% and 7.01% for *S. haemolyticus* and *P. aeruginosa*, respectively.⁸⁰ The degradation of polystyrene MPs using edible fungi was also studied by Yu *et al.* and the highest degradation rate (16.17 ± 8.87%) was found with *Pleurotus ostreatus* after 50 days of fungal degradation.⁸¹

It may be noted that several studies have reported different biological methods for the removal of MPs, still physical and chemical methods for the removal of MPs are more reliable, efficient and economical.



Table 1: Comparative analysis of different techniques for the removal of MPs

| Method | Key features of the method | Specific example | Type of target MP | Size range of targeted MPs | Surface charges on the adsorbent | Pore/ mesh size of the adsorbent | Degradation time | % MPs removal efficiency | Removal mechanism | Ref. |
|-----------------------------------|---|--|--|----------------------------|--------------------------------------|----------------------------------|------------------|--------------------------|--|---------------|
| Photocatalytic degradation | Durable and eco-friendly | Nb-doped SnO ₂ QDs | Polyethylene | 350 μm | -35 mV | - | 7 h | 28.9% | Interactive mechanism of dual defects and photocatalytic mechanism | ⁸² |
| Electrochemical oxidation | Highly efficient; does not require the use of toxic chemical agents | CeO ₂ -PbO ₂ -0.005 anode | Polyvinyl chloride | - | - | - | 6h | 38.67% | Ce(III)/Ce(IV) valence-modulated mechanism | ⁸³ |
| Coagulation | Minimum energy uses for the removal of tiny MPs | Polyaluminum ferric chloride with Opuntia Milpa Alta particles | Polystyrene | 2–10 μm | 4.52 mV at pH 6 and -0.56 mV at pH 9 | 380 μm | 60 min | 94.8% | Charge neutralization and adsorption bridging | ⁸⁴ |
| Electrocoagulation | Economical and energy-efficient; does not require chemical coagulants; efficient for removing small MPs | Al/Fe-graphene-Electrocoagulation (EC) system | Polyethylene Terephthalate, Polypropylene, and Polystyrene | 45 μm to 250 μm | - | - | 120 min | 96 % | Adsorption and electrostatic interactions | ⁸⁵ |





| | | | | | | | | | | |
|----------------------------|--|---|--|--|-----------------------|------------------|--------|---------|---|---------------|
| Sand filtration | Cost-Effective and simple to operate | Natural quartz sand in a Rapid Sand Filtration (RSF) system | Polypropylene and Polystyrene | <10 μm | -30.1 mV and -32.8 mV | NA | 20 min | 84–98 % | Synergistic combination of physicochemical sorption | ⁵⁹ |
| Disc filtration | Minimum energy consumption for the accelerative removal of MPs | Disc Filter | Polyethylene, polystyrene, polyester, polyvinyl chloride | > 300 μm | - | 15 μm | - | 89.7% | MPs removal by high-pressure back-flushing | ⁸⁶ |
| Ozonation | Cost-effective and efficient | $\alpha\text{-MnO}_2$ and $\alpha\text{-FeOOH}$ | Polystyrene | < 1 μm | - | - | 8h | 16.5% | A free radical mechanism | ⁷¹ |
| Froth flotation | Low cost, and adaptable for quick operation | Flotation process combined 10 g/ton of sodium oleate | Polyvinyl chloride, acrylonitrile–butadiene styrene | 0.074 μm to 5 μm | -33.1 t0 - 14.5 mV | - | 24h | 100% | Hydrophilization and electrostatic mechanism | ⁸⁷ |
| Oil film separation | Affordable and simple to use | Castor Oil | Polypropylene, Polystyrene, polymethyl methacrylate, and glycol modified | 0.3–1.0 mm | - | 25 μm | 4h | 99% | lipophilicity-based protocol | ⁸⁸ |

| | | | | | | | | | | |
|---------------------------------------|--|---|----------------------------|----------------------|----------------------|----------------|---------|--------|--|---------------|
| | | | polyethylene terephthalate | | | | | | | |
| Biochar filters | Effective in achieving excellent adsorption capacities | Surface-engineered palm kernel shell biochar | Polyethylene, polyamide | 159 nm–48 μ m | +9.5 to +14.1 mV | 0.6 to 1.18 mm | 2h | 96.12% | Electrostatic interaction, hydrophobic interaction, π - π interaction and hydrogen bonding | ⁸⁹ |
| Adsorption removal | Cost-effective, easy to use and reusable upto many cycles | Polydopamine-modified sodium alginate hydrogel | Polyethylene, polystyrene | 200 nm to 10 μ m | -17.9 \pm 2.2 1 mV | - | 2h | 99.6 % | Chemical adsorption, electrostatic interactions, hydrogen bonding and π - π interactions | ⁹⁰ |
| Membrane bioreactor technology | Precise removal of contaminants at variable MPs concentration ensuring effective removal | Living membrane bioreactor containing biological layer as a membrane filter | Polyethylene | \leq 20 μ m | - | 0.04 μ m | 21 days | 95% | Electrocoagulation and adsorption | ⁷⁸ |



5. Hydrogels and their application in removal of MPs

In recent years, hydrogels have piqued the interest of scientists for addressing the critical issue of MPs pollution. Hydrogels leverage their high water-holding capacity and porous architecture to elevate the capture and removal of MPs. They can effectively eliminate MPs from water by simple adsorption, surpassing limitations of conventional removal techniques and unlocking new possibilities to improve water quality.

5.1. Salient features of hydrogels

Hydrogels are 3D crosslinked networks of polymeric chains that can absorb and retain significant amount of water without dissolving.⁹¹⁻⁹² These materials exhibit exceptional properties including high porosity, structural flexibility, elasticity, and tunable functionality. Additionally, the possibility of incorporating the features of biocompatibility and biodegradability by a suitable choice of components and synthetic strategy, makes them an ideal candidate for green adsorbents.⁹³⁻⁹⁴ **Fig. 3** summarizes a few examples of different building blocks (e.g., polymers, monomers, comonomers, and crosslinkers) that have been widely utilized for the fabrication of hydrogels.⁹⁵⁻¹⁰²

Hydrogels can be synthesized using various natural and synthetic polymers. Usage of synthetic polymers offers reproducibility and control over the molecular weight of polymer chains, while natural polymers are employed to utilize their inherent biocompatibility and biodegradability.¹⁰³⁻¹⁰⁴ Additionally, a combination of natural and synthetic polymers is also frequently investigated to develop hybrid hydrogels that are benefitted from the advantages of both types of polymers.¹⁰³⁻¹⁰⁴ Moreover, the incorporation of different functional groups (e.g., $-\text{NH}_2$, $-$



COOH, –OH, –CONH₂) inside the hydrogels during synthesis can enhance their interaction with the guest moieties including NPs and MPs, thus facilitating their effective removal.¹⁰⁵⁻¹⁰⁹


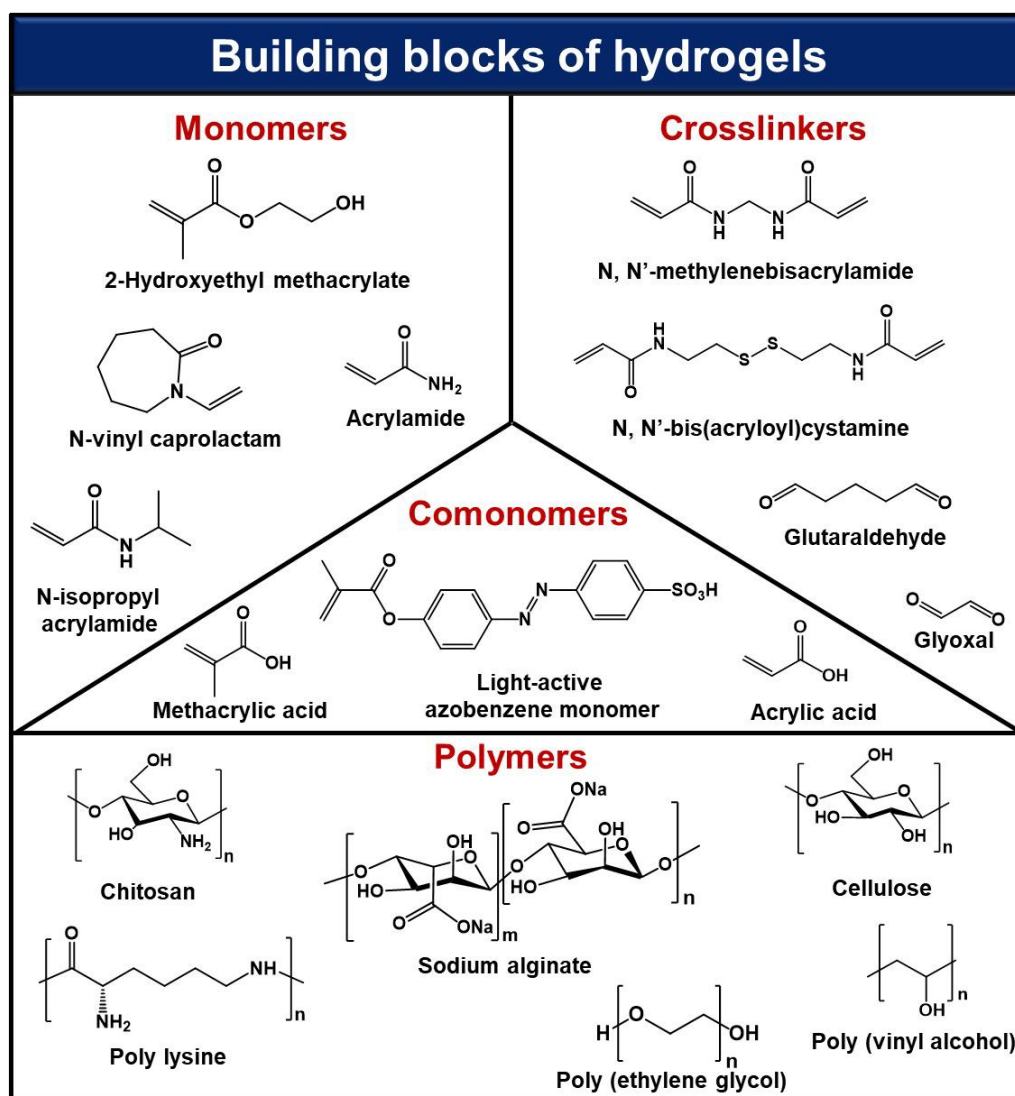


Fig. 3: Examples of key components utilized for the fabrication of hydrogel: Monomers, comonomers, crosslinkers and commonly used polymers.

Further, hydrogel networks are typically formed via physical or chemical crosslinking of polymeric chains.¹¹⁰⁻¹¹¹ Physical crosslinking involves hydrogen bonding, electrostatic interactions, hydrophobic/hydrophilic interactions, metal coordination,



crystallization/stereocomplex formation, and π - π stacking interactions.¹¹¹ In the case of chemical crosslinking, formation of covalent or dynamic covalent bonds takes place providing a control over the mechanical strength and degradability of hydrogels.¹¹⁰ Various dynamic covalent bonds including imine,¹¹² disulfide,¹¹³ boronic ester,¹¹⁴ and acylhydrazone¹¹⁵ have been utilized in the literature for the fabrication of degradable hydrogels. These dynamic bonds get degraded under specific environmental conditions, reducing the risk of secondary pollution that is often associated with persistent synthetic materials.^{116-118, 83-85}

5.2. Hydrogels for removal of MPs

In recent years, scientists have explored various natural, synthetic, and natural/synthetic hybrid polymers-based hydrogels to mitigate MPs pollution. However, the removal efficiency of hydrogels is strongly affected by the pore size of hydrogel, swelling behaviour, network density and overall accessible surface area.¹¹⁹ In addition, the size, shape, and surface charge of the target MPs also affects the removal efficiency.¹²⁰

Taking advantage of the attractive features of hydrogels mentioned earlier, Patel *et al.* reported aluminium and iron-incorporated ionotropic chitosan (CS) hydrogels for the removal of PET MPs.¹²¹ Here, the integration of metal cations into CS hydrogels boosted their ionic charge, thus providing a straightforward and efficient method to enhance the adsorption capacity, while offering low cost and minimal environmental impact. Interestingly, a pH-based alteration of the adsorption capability of both Al-CS and Fe-CS hydrogels was observed here. At lower pH, the protonation of amino groups in CS combined with the formation of cationic metallic species (e.g., Al^{3+} , $\text{Al}(\text{OH})_2^+$, $\text{Al}(\text{OH})_2^+$, FeO^+) enhanced the overall positive charge of hydrogels, which in turn helped in achieving higher electrostatic interaction with anionic MPs, leading to a 70% adsorptive



removal of PET MPs. While at higher pH, deprotonation of amino groups in combination with the generation of anionic hydrates (like $\text{Al}(\text{OH})_4^-$, $\text{Al}(\text{OH})_3$, FeO_2^- , FeO_2H) led to repulsion, thus reducing the adsorption efficiency. Moreover, upon increasing the doping concentration, adsorption efficiency was comparatively reduced which could be attributed to the cations occupying the pore regions of hydrogels. Finally, the successful removal of MPs from CS-based hydrogels using NaOH demonstrated the reversibility of adsorption–desorption, confirming that the process was governed by physical adsorption.¹²¹

Utilizing copper substituted polyoxometalate (Cu-POM) nanoclusters, Dutta *et al.* synthesized Cu-POM infused triple interpenetrating network hydrogel (pGel@IPN), which was composed of polyaniline (PANI), PVA, and chitosan (CS).¹²² This hydrogel matrix exhibited excellent mechanical strength which can be assigned to strong electrostatic interactions between positively charged PANI and negatively charged Cu-POM. The hydrogel was further strengthened by crosslinking between hydroxyl groups of PVA and aldehyde groups of glutaraldehyde (GA) (**Fig. 4**). pGel@IPN demonstrated high removal efficiency for both PVC and PP-based MPs which were labelled with Nile red for their easy detection and analysis via fluorescence microscopy. pGel@IPN showed ~95% and ~93% removal efficiency for PVC and PP MPs, respectively, at pH 6.5. Statistical analysis further revealed that the adsorption of MPs followed Langmuir model ($R^2 > 0.99$), suggesting monolayer sorption of MPs on hydrogel surface. Notably, the adsorption capacity of hydrogel was high, reaching 321.87 mg g^{-1} for PVC and 144.29 mg g^{-1} for PP MPs. These hydrogels demonstrated good reusability to capture MPs up to five cycles. Further, UV-induced degradation of MPs was facilitated by taking advantage of the catalytic properties of Cu-POM, thus combining the concept of efficient capturing and degradation of MPs. Finally, after the



hydrogel served its purpose, it was upcycled into carbon nanoparticles, which in turn were utilized as an adsorbent to remove Cr (VI) from contaminated water to move towards circular economy.¹²²

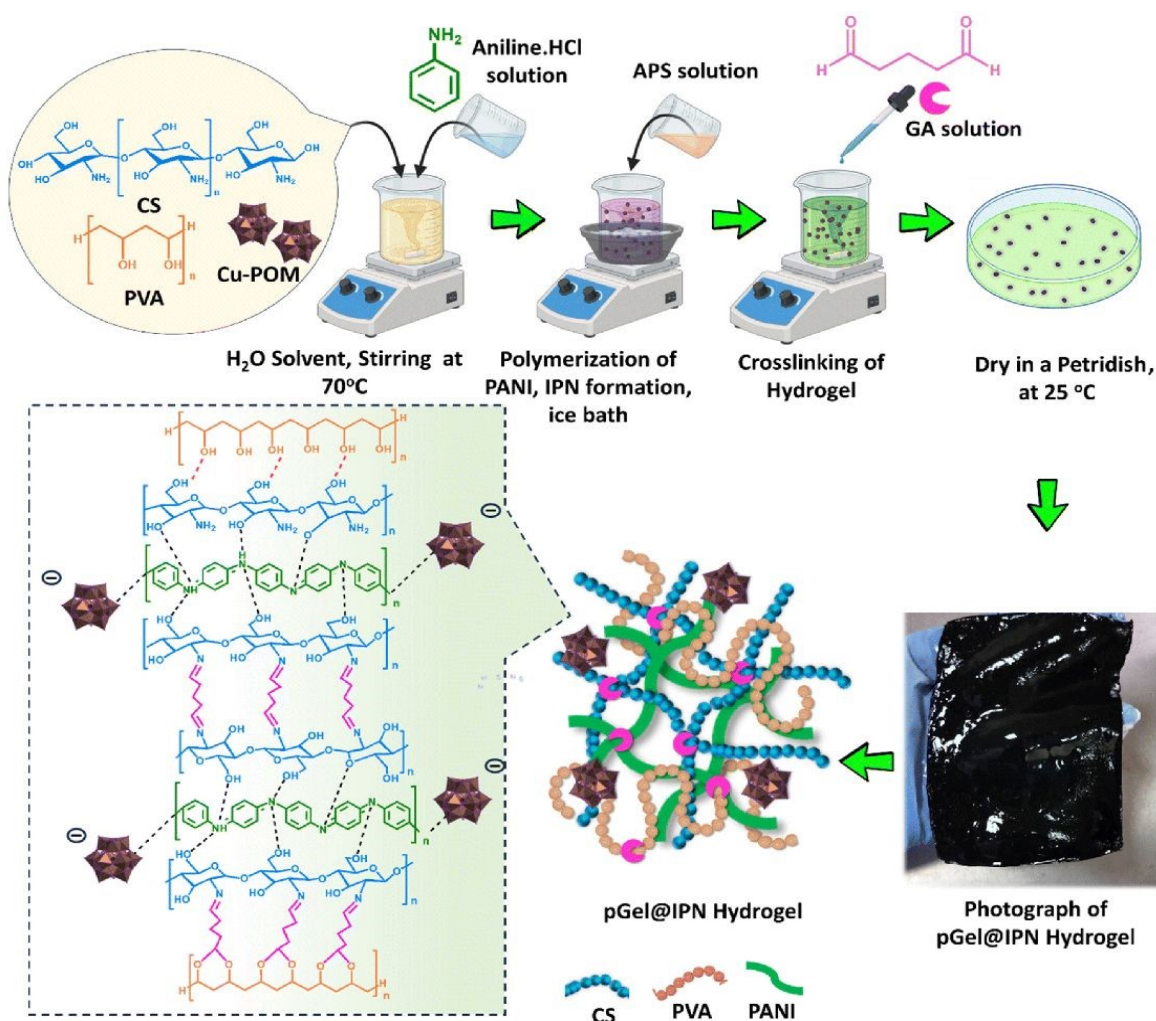



Fig. 4: Scheme showing the step wise synthesis of copper substituted polyoxometalate (Cu-POM) nanoclusters infused triple interpenetrating network hydrogel (pGel@IPN). Reproduced with permission.¹²² Copyright 2024, Publisher Royal Society of Chemistry.

Developing biomass derived natural polymers-based hydrogels offers a sustainable approach to capture MPs for water treatment. In this regard, Li *et al.* utilized bamboo-derived lignin in combination with PVA to synthesize a hydrogel for the removal of PS MPs.¹²³ Here,



lignin was subjected to phenolization and ammonization processes that markedly increased the phenolic hydroxyl and long-chain amino groups content in lignin, respectively. The incorporation of amino groups introduced dual functionality in lignin including pollutant adsorption over a broad pH range and improved encapsulation. Aminated lignin/epichlorohydrin/polyvinyl alcohol (LG-GH-PVA) hydrogel was synthesized via chemical crosslinking of aminated lignin with epichlorohydrin, as well as ionic crosslinking of PVA with Ca^{2+} . The adsorption process followed a pseudo-second-order kinetic model, while the equilibrium data exhibited the best fit with Langmuir isotherm confirming a monolayer adsorption with a maximum adsorption capacity of 288.6 mg/g. Notably, the hydrogel maintained 87.6% of its adsorption capacity even after five regeneration cycles which was attributed to π - π interactions between hydrogel and PS MPs in addition to hydrogen bonding between hydroxyl, carboxyl, and amino groups present on both the surfaces. The reported hydrogel demonstrated high adsorption of PS MPs in real-world systems, achieving efficiencies of 90.6–92.7% in lake water, 92.2–94.7% in pipeline water, 94.6–97.1% in river water, and 95.5–97.9% in sludge supernatant. In addition to PS MPs, the hydrogel effectively adsorbed four other MPs including PEI MPs, PP MPs, PVC MPs, and PA MPs even at a low concentration of 10 mg/L, presenting itself as a promising platform for MPs removal.¹²³

Exploring other natural polymers, Leppanen *et al.* developed cellulose-based hydrogels by using two different grades of cellulose nanofibrils including native cellulose nanofibrils (CNF) and TEMPO-oxidized CNF.¹²⁴ These hydrogels were utilized to capture both cationic and anionic PS particles (1 μm and 100 nm) using a microfluidic setup coupled with fluorescence microscopy (**Fig. 5a-b**). It was reported that the adsorption and removal of PS particles were influenced by the hygroscopic cellulose network and large surface area of hydrogels.¹²⁴ The removal mechanism was based on the attractive surface interactions when capillary forces were not assisting the



capturing process. The larger surface area and enhanced surface interactions were the driving forces for the cohesion between material surface and NPs here. Next, Yi *et al.* developed dual crosslinked chitin (Ch) nanofibrils-based hydrogels by using formaldehyde for chemical crosslinking and ammonia fumigation for physical crosslinking using freeze thaw method (**Fig. 5c**).¹²⁵ The dual crosslinked hydrogels exhibited higher mechanical strength and filtration efficiency as compared to individual physically or chemically crosslinked hydrogel. Moreover, a syringe-based filtration device using the dual crosslinked nanoCh hydrogels was prepared which could achieve almost complete removal of MPs (size $\sim 3 \mu\text{m}$) with highest flux of $8.22 \text{ mL cm}^{-2} \text{ h}^{-1}$ owing to the larger pore size and robust channel structure, offering scalability for large-scale water purification. Finally, after filtration, the SEM images of nanoCh hydrogel (top side and down side) were captured which clearly depicted the presence of adsorbed MPs on the top surface indicating their effective removal (**Fig. 5c**).¹²⁵ The porosity of the dual-crosslinked nanochitin hydrogels was $257.5 \text{ m}^2 \cdot \text{g}^{-1}$ and carries rich pores in the microscale range explaining the effective particle interception both on the surface and within the hydrogel structure with a flux of $8.22 \text{ mL cm}^{-2} \text{ h}^{-1}$.¹²⁵ Overall, the use of these systems for the elimination of MPs could pave a new pathway for next-generation portable wastewater treatment methods.



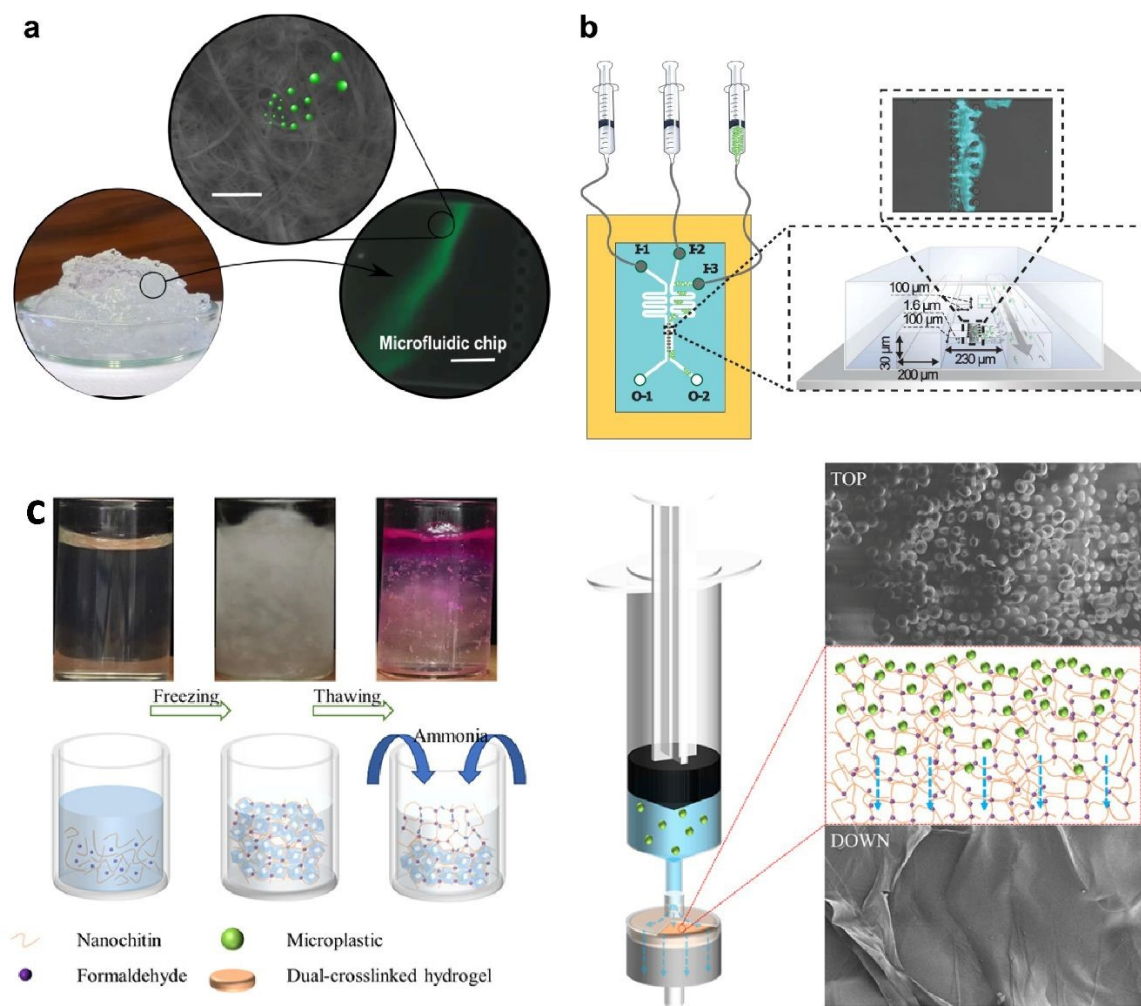


Fig. 5: (a) Schematic representation of a proof of concept for capturing fluorescently labelled MPs by CNF hydrogel using a microfluidic set-up coupled with fluorescent imaging (Scale bar in SEM image is 1 μm and 25 μm in microfluidic chip image). (b) Microfluidic setup for CNF hydrogel containing trap showing the injection of fluorescent MPs and water. Reproduced under the CCBY-license.¹²⁴ Copyright 2022, Publisher Nature Portfolio. (c) Images, illustration of synthetic protocol of nanoCh hydrogels, and the syringe-based filtration device using dual crosslinked nanoCh hydrogel (Inset: SEM image of the top side and down side of the nanoCh hydrogel after filtration). Reproduced with permission.¹²⁵ Copyright 2025, Publisher Elsevier.



Considering nature-inspired catechol-based chemistry, Han *et al.* fabricated polydopamine (PDA)-modified sodium alginate hydrogel (PMSAH) for eliminating MPs from drinking water.⁹⁰ Here, PDA-modified sodium alginate was crosslinked using calcium ions and tested for the elimination of different MPs including PE and PS of varying size and surface charges (**Fig. 6**). For real life application, PMSAH was also utilized for the removal of MPs generated by boiling the commercially available tea bags. It was reported that PMSAH exhibited the highest removal efficiency of ~99.6% which could be attributed to various intermolecular interactions, including hydrogen bonding, electrostatic interactions, hydrophobic interactions, and π - π stacking interactions offered by PDA (**Fig. 6**).⁹⁰


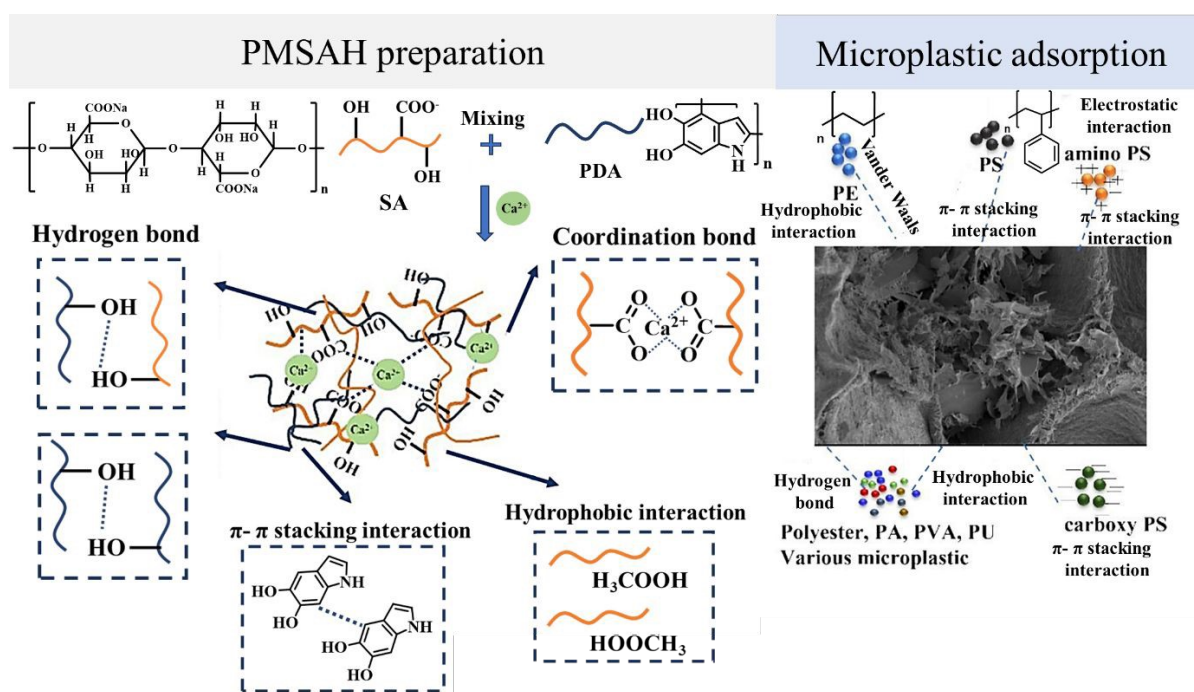


Fig. 6: Schematic representation for the fabrication of PMSAH hydrogel and interactions involved in MPs adsorption. Adapted with permission.⁹⁰ Copyright 2025, Publisher Elsevier.

Taking a step further in the direction of combined adsorption, detection, and actuation performance while still considering the catechol-based chemistry, Guo *et al.* imparted hydrogels



with stimuli responsiveness and multiple functionality to improve their performance for heavy metal adsorbed MPs remediation.¹²⁶ In this case, a smart light-driven multifunctional hydrogel actuator was engineered for selective removal of iron adsorbed polystyrene microplastics ($\text{Fe}^{3+}@PS$) from water.¹²⁶ Here, covalently bonded acrylated polyethyleneimine and polydopamine copolymer (M-PEI@PDA), graphene oxide (GO) nanosheets, and poly(*N*-isopropyl acrylamide) (PNIPAM) formed hierarchical interpenetrating network of hydrogel (M-PEI@PDA/GO/PNIPAM) (**Fig. 7a**). M-PEI@PDA copolymer was prepared utilizing Michael addition providing fluorescence responsiveness to the hydrogel. Subsequently, multifunctional crosslinked hydrogel was fabricated via *in situ* radical polymerization between thermo-responsive NIPAM monomer, M-PEI@PDA copolymer and *N, N'*-methylene bisacrylamide (MBA) crosslinker (**Fig. 7a**). Notably, hydrogel showed strong interfacial interactions between catechol and amino groups of polymer and $\text{Fe}^{3+}@PS$, offering an excellent reversible adsorption property (**Fig. 7b**). Furthermore, by leveraging temperature responsiveness of PNIPAM, hydrogel actuator demonstrated excellent actuation performance (bending speed: 2–4°/s, and swimming speed: 0.5 mm/s), thus facilitating the locomotive adsorption of MPs present in water (**Fig. 7b**). The reported hydrogel displayed an ultralow detection for ferric ion (0.98 μM) and selective adsorption for $\text{Fe}^{3+}@PS$ (~97%) with high adsorption (~95%) and desorption efficiency (~99%) for MPs, making it a suitable candidate to remove MPs from water.¹²⁶



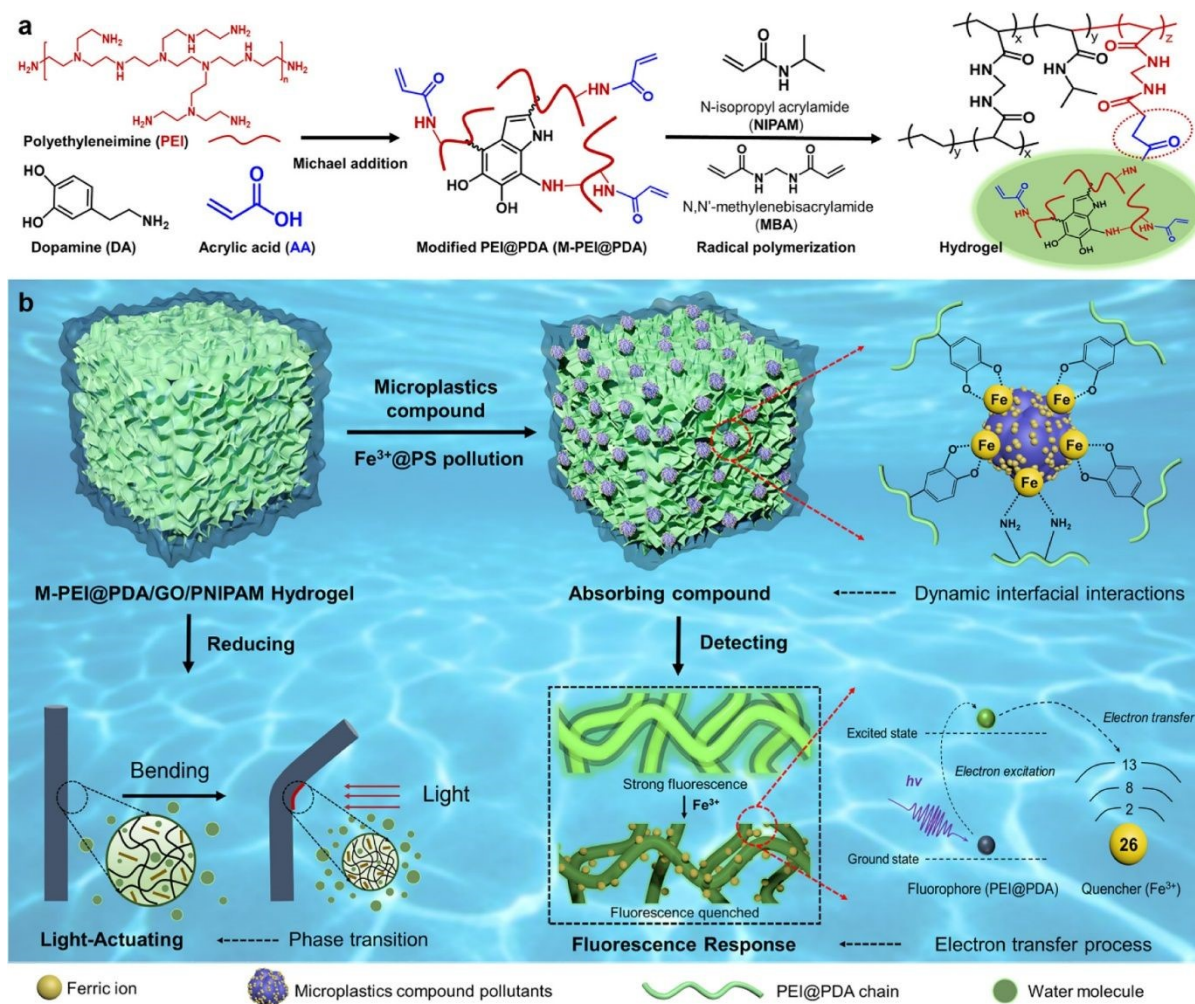


Fig. 7: (a) Schematic illustration for the fabrication of M-PEI@PDA/GO/PNIPAM-based multifunctional hydrogel. (b) Multifunctional hydrogel with combined adsorption, detection, and actuation performance for efficient removal of Fe³⁺@PS. Reproduced with permission.¹²⁶ Copyright 2022, Publisher American Chemical Society.

6. Sponges for removal of MPs

In addition to hydrogels, hydrogel derived sponges have recently gained attention as a promising alternative for MPs removal owing to their highly porous structure, light weight, and good adsorption capacity. The sponges are typically fabricated by drying hydrogels using freeze drying



method. For example, Sun *et al.* synthesized graphene oxide-incorporated chitin-based (ChGO) sponges by freeze-drying of corresponding hydrogel having epichlorohydrin-based crosslinking.¹²⁷ ChGO sponges could be reused and showed high adsorption efficacy of 89.8%, 72.4%, and 88.9% for PS, carboxylated polystyrene (PS-COOH), and aminated polystyrene (PS-NH₂) MPs, respectively, after 3 adsorption–desorption cycles. The pore size of the sponge was between 50–76 μm and it was capable of accommodating polystyrene MPs (1 μm in size) upto 3 cycles without any degradation. Here, the adsorption of MPs was facilitated by hydrogen bonding, electrostatic interactions, and π - π interactions between MPs and ChGO sponges. Additionally, biodegradation results also confirmed the degradability of ChGO sponges by microorganisms present in soil.¹²⁷ Taking a step further, Sun *et al.* developed various chitin-based sponges including pure chitin (Ch), chitin/O-C₃N₄ (ChCN), chitin/GO (ChGO), chitin/GO/carboxymethyl cellulose (ChGO-CL), and chitin/GO/chitosan (ChGO-CS)¹²⁸. It was reported that the incorporation of additional material in chitin sponges further improved their mechanical strength and adsorption capacity. The pore size of the prepared sponges varied between 86 μm to 181 μm , and the sponges were efficient to remove different functionalized PS MPs (~1 μm) with removal efficiencies ranging from ~71% to ~92%. Moreover, these sponges could be reused up to three cycles for MPs removal.¹²⁸

Next, Zhu *et al.* introduced polyaniline (PANI) into chitin matrix crosslinked with epichlorohydrin to develop chitin/polyaniline sponge (ChPANIs) having macroporous structure with uniform network.¹²⁹ It was reported that upon increasing the hydrophilicity of PANI in ChPANIs, the removal efficacy of polystyrene MPs (size = 1 μm) was enhanced from 84% to 91%, which could be attributed to better dispersibility of PANI in chitin-based sponge matrix with porous structure ranging from 190 μm to 470 μm . More hydrophilic PANI in ChPANIs provided



more contact area and adsorption sites, which enhanced the electrostatic interactions with MPs, providing excellent adsorption performance. Further, SEM images demonstrated that ChPANIs efficiently removed MPs without causing significant alterations in its sponge-like morphology, whereas higher magnification clearly confirmed numerous MPs adhered to the surface. The adsorption of MPs followed the Freundlich isotherm, suggesting multi-layer adsorption of MPs on ChPANIs. Moreover, ChPANIs demonstrated good mechanical strength, reusability up to five cycles, and ~89% degradation over 15 days in soil once their purpose is served.¹²⁹

Nowadays, fibrous sponges have gained significant interest for the removal of MPs. In this direction, Wu *et al.* demonstrated that a fibrous framework sponge derived from exfoliated β -chitin nanofiber and suspended cellulose fiber can be derived simply through hydrogen bonding without the use of any crosslinking agents (**Fig. 8a**). The fibrous sponge was prepared by interrupting original hydrogen bonds in the presence of an acid, stripping cotton into finer cellulose fibers, exfoliating the chitin into nanofibrous plane, and then interlacing these fibers to induce intermolecular hydrogen bonds. The fabricated sponge demonstrated a porous interconnected structure in addition to numerous activated functional groups such as OH^- , NH_3^+ , and NHCO^- . The presence of these functional groups assured the removal of MPs through multilevel interactions, including electrostatic interactions, hydrogen bonding and Van der waals interactions (**Fig. 8b**). The fabricated sponge demonstrated 98.0% to 99.9% MPs removal efficiency and was reusable upto five adsorption-desorption cycles without any effective loss in the degradation efficiency.¹³⁰




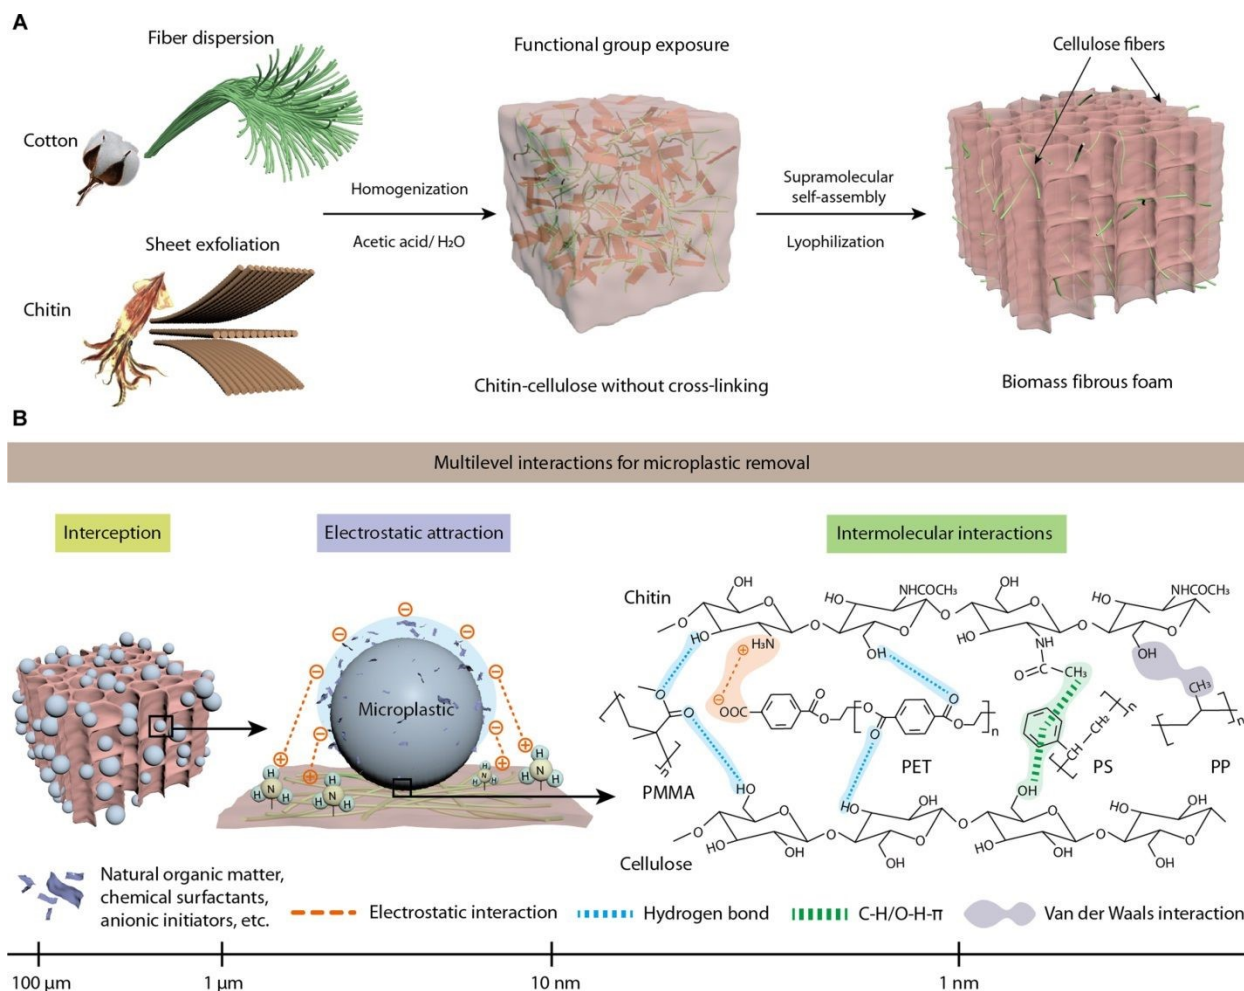


Fig. 8: (a) Schematic illustration of self-assembly of chitin/ cotton fibrous foam, and (b) Mechanistic pathway showing multilevel interactions for the removal of MPs. Reproduced with permission.¹³⁰ Copyright 2024, Publisher Science.

Further, Ko *et al.* utilized freeze-drying method coupled with genipin (GP)-based crosslinking to fabricate cost effective, and light-weight graphene oxide/chitosan/genipin sponges (GO₅/CS/GP).¹³¹ These sponges were macroporous (porosity = 95%, pore size = $58.3 \pm 47.8 \mu\text{m}$, density = 32.6 mg/cm^3) and exhibited an excellent capturing rate ($\sim 73\%$) for PS NPs of diameter $0.026 \mu\text{m}$ as compared to PS MPs of diameter $1.1 \mu\text{m}$ ($\sim 41\%$). The adsorption of PS MPs on GO₅/CS/GP was attributed to hydrogen bonding, pore filling interaction, hydrophobic interaction,



and π - π interaction. This work highlighted the need of developing systems that can be used for efficient removal of NPs.¹³¹

Similarly, Risch *et al.* performed freeze drying of chitosan electrospun nanofibers-based suspension followed by crosslinking with GA to develop chitosan nanofiber sponges (CSNFs) having good water stability.¹³² CSNFs exhibited a bulk density of 5.77 mg cm⁻³, pore diameter 163 ± 41 μm and a porosity of 99.59%. The hierarchical pore structure of CSNFs was utilized to remove PET MPs and Arizona test dust (ISO 12103-1) suspensions. These sponges exhibited high selectivity for the adsorption of PET MPs from water with ~99% removal efficiency, suggesting their application in tackling MPs based pollution.¹³²

In another direction, taking inspiration from anisotropic vessels in hardwood, Xu *et al.* developed biomimetic, double crosslinked CS-based sponges (BGCS) by combining directional freezing with freeze drying and GA-based crosslinking.¹³³ Here, sponges were reinforced with flexible bacterial cellulose fibrils, which served as physical crosslinkers by forming supramolecular assemblies with chitosan (soft phase). Additionally, treatment with GA vapor further resulted in covalently crosslinked network (hard phase) in sponges (**Figure 9a**). Moreover, BGCS sponge displayed excellent wet compressive resilience with retention rate of ~95% even after 100 compression cycles. It was reported that the anisotropic structure of sponges served as a rapid water treatment channel and removed ~78% of PS MPs (~1 μm in size) within 420 min at room temperature. Owing to its higher wet compressibility, the developed sponge demonstrated good removal efficiency for PS MPs (~47%) even after 20 cycles (**Figure 9b**). Here, electrostatic interactions, conjugation, and intraparticle diffusion were identified as primary forces for adsorption of PS MPs on sponges.¹³³



Building on the concept of enhancing mechanical strength and improving water stability via crosslinking, Ma *et al.* synthesized Ca^{2+} crosslinked sodium alginate-based sponges via secondary freeze-drying method.¹³⁴ These sponges exhibited excellent water absorption (~1193–5232%), high porosity (~89%), good mechanical properties, and remarkable PS MPs ($\leq 5 \mu\text{m}$) removal efficiency (~92%). The adsorption of MPs on sponges was attributed to intra-particle diffusion, hydrogen bonding, and π - π interactions. Overall, the above-mentioned examples clearly signify the potential of polymeric sponges in addressing the issue of MPs pollution for moving towards sustainable development.

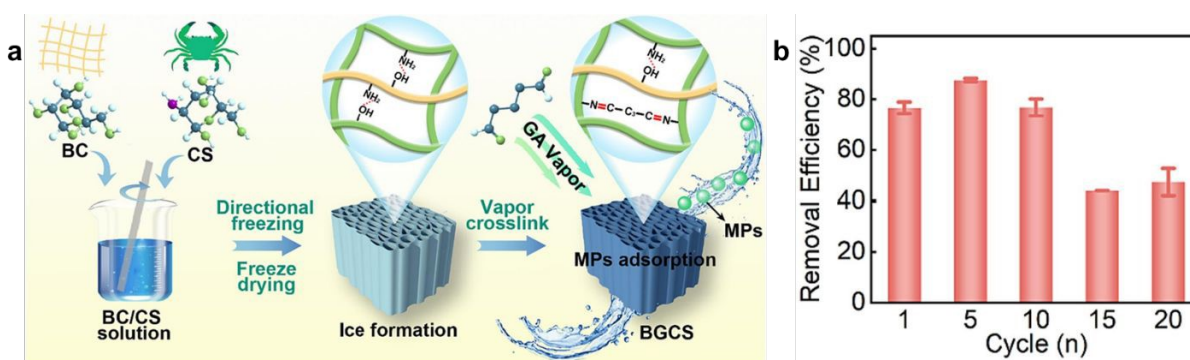


Fig. 9: (a) Synthetic route for the fabrication of biomimetic, double crosslinked chitosan-based sponges (BGCS). (b) Histogram showing the efficiency of BGCS in removing PS MPs up to 20 cycles. Reproduced with permission.¹³³ Copyright 2023, Publisher Elsevier.

7. Electrospun fibers-based membranes for removal of MPs

In recent years, electrospun polymeric nanofiber-based membranes have emerged as a potential candidate for water purification. These membranes display high surface area to volume ratio, highly interconnected pore structure, and adjustable physicochemical properties (e.g., wettability) that helps in increasing the fluid flow rate while reducing the fouling.¹³⁵⁻¹³⁸ In the literature, nanofibrous membranes have been developed through electrospinning of both natural and




synthetic polymer-based solutions.¹³⁹⁻¹⁴⁰ Morphology and architecture of these electrospun fibers can be tuned by adjusting several parameters including polymer solution related parameters (concentration, viscosity, and conductivity), electrospinning process parameters (flow rate, voltage, and distance between spinneret and collector), and environmental parameters (temperature or humidity).^{139,141} The resulting fibrous mat can also be processed to form dispersion of nanofibers which in turn can be used for the preparation of sponges or wet-laid membranes.¹⁴²⁻¹⁴³ So far, electrospun fibers-based membranes have been widely explored for removing organic and inorganic pollutants including heavy metal ions, dyes, and oil from aqueous environment due to their large surface area and adjustable wettability.¹⁴⁴⁻¹⁴⁵ The main driving force behind the removal of pollutants from aqueous environment is adsorption. Recently, scientists have started to explore electrospun nanofibers-based membranes for the removal of MPs.

In this direction, Wang *et al.* fabricated polyacrylonitrile (PAN)-based nanofiber membranes by electrospinning followed by hot-pressing method.¹⁴⁶ Fiber diameter, membrane thickness, and membrane porosity were optimized here by adjusting various processing parameters. These membranes were utilized for the removal of PS beads (0.2 μm and 0.1 μm) from water. It was reported that the rate of rejection of membranes for 0.2 μm PS beads approached ~100% upon reducing the porosity of membrane. Moreover, membranes with relatively small nanofiber diameters were able to completely reject all the 0.1 μm PS beads while maintaining high flux and low degree of fouling. This study demonstrated that the fiber diameter and membrane porosity play crucial role in determining the equivalent/apparent pore size, which in turn directly relates to microfiltration performance.¹⁴⁶

With the aim of developing self-standing membrane without any supporting substrates, Juraj *et al.* developed polyurethane/graphene oxide-montmorillonite-based electrospun composite



(PGT) membrane (**Figure 10a**).¹⁴⁷ Here, different amounts of graphene oxide-montmorillonite (GOMt) ranging from 5 to 20 wt% were loaded into PGT membrane. Based on high tensile strength (6.6 MPa), porosity (~61%), superhydrophilicity, pressure-driven water flux (8163 L m⁻² h⁻¹), and higher gravity-driven water flux (793 L m⁻² h⁻¹), PGT membrane containing 20 wt% GOMt was chosen for MPs and NPs separation from water. For separation studies, three individual dispersions of MPs and NPs were prepared including acrylonitrile butadiene styrene MPs (ABS MPs), PS NPs, and poly(methyl methacrylate) NPs (PMMA NPs). Experimental results showed that ABS MPs, PMMA NPs, and PS NPs followed cake formation ($R^2 = 0.9997$), intermediate blocking ($R^2 = 0.9998$), and standard blocking ($R^2 = 0.9907$) fouling mechanism, respectively. Here, removal efficiencies for ABS MPs, PMMA NPs, and PS NPs were 98%, 97%, and 95%, respectively. In the case of ABS MPs, constant flux was observed due to easy removal of cake layer from membrane. However, flux reduction was reported in the case of PMMA NPs (385.87 L m⁻² h⁻¹) and PS NPs (395 L m⁻² h⁻¹) filtration owing to the adherence of NPs on the membrane (**Figure 10b**). Overall, this electrospun fibers-based membrane showed good performance for the separation of both MPs and NPs upto 10 cycles, further confirming its reusability. In addition to MPs and NPs removal, the membrane also exhibited selective adsorption capacity of methylene blue (MB) (417 mg g⁻¹) from methylene blue/methyl orange (MB/MO) mixture, thus rendering itself as a promising candidate for water purification.¹⁴⁷ ABS MPs followed the cake formation mechanism with $R^2 = 0.9997$, while the intermediate blocking mechanism was the predominant mechanism in case of PMMA NPs ($R^2 = 0.9998$) and PS NPs ($R^2 = 0.9907$). This may be due to the reason that the size of ABS MPs (624 nm) is greater than the pores of the electrospun composite, which favours the formation of a cake layer and causes extensive relative flux decay (85%) during the filtration of ABS MPs. Here, cake formation was responsible for the efficient



removal efficiencies of ABS MPs. On the contrary, in the cases of PS NPs and PMMA NPs, electrostatic interactions between negatively charged electrospun composite fibers (ζ potential = -42 mV) and positively charged NPs (ζ potential = $+38$ mV for PS NPs and ζ potential = $+41.7$ mV for PMMA NPs) were responsible for the removal of NPs.¹⁴⁷

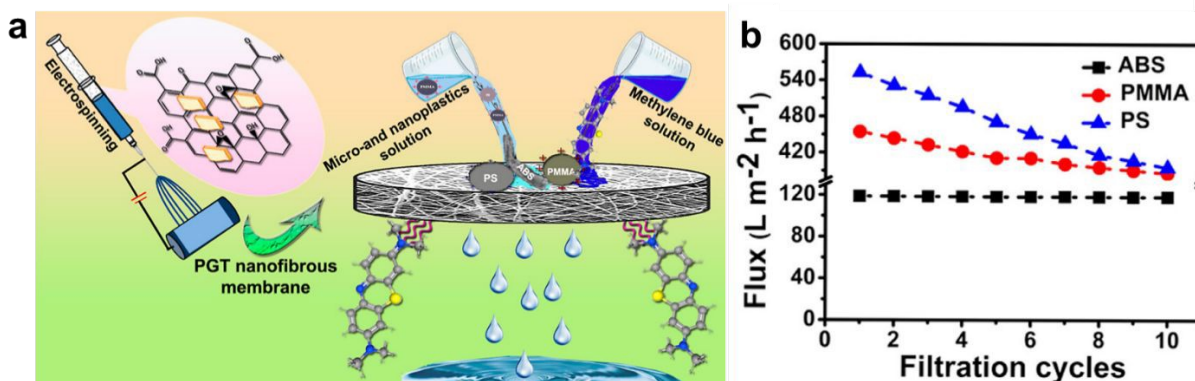


Fig. 10: (a) Schematic representation showing PGT-based electrospun composite membrane for the removal of MPs, NPs, and MB from water. (b) Graph showing variation in flux associated with the reusability study of the PGT electrospun membrane up to 10 filtration cycles. Reproduced with permission.¹⁴⁷ Copyright 2023, Publisher American Chemical Society.

Taking a step further, Rist *et al.* developed self-standing electrospun fiber membranes from bio-based polyamide 6.9 (PA@EFMs).¹⁴² Here, polyamide 6.9 was prepared using hexamethylene diamine and azelaic acid derived from plant oil. PA@EFMs exhibited good mechanical strength and high resistance to solvents. Highly porous architecture of PA@EFMs (pore diameter = 0.55 μm to 1.14 μm) showed remarkable efficacy of $>99.7\%$ for the filtration of PS MPs (~ 679 nm) from water. Additionally, the high hydrophobicity of PA@EFMs facilitated efficient adsorption of oil from water, achieving separation efficacy of 99.9% , while retaining a high permeate flux of 5345 $\text{L m}^{-2} \text{h}^{-1}$. Furthermore, the recyclability of PA@EFMs was demonstrated through back flushing, highlighting sustainable potential of these membranes.¹⁴²



Next, to enhance the structural integrity of electrospun membranes, Gopakumar *et al.* fabricated electrospun fibers of PVA which were crosslinked with GA to form stable nanofibrous membrane.¹⁴⁸ MPs removal efficacy of the membrane was evaluated using PE MPs ($5\ \mu\text{m} \leq d \leq 25\ \mu\text{m}$) (~99% removal efficiency) and PS MPs ($d \leq 1\ \mu\text{m}$) (~77% removal efficiency). Furthermore, excellent recovery in performance was observed by backwashing even after five cycles, thus showcasing the durability and reusability of PVA membrane. Additionally, the membrane displayed ~69% removal efficiency for lead at pH 6, demonstrating its capability to handle water pollution from different fronts.¹⁴⁸

In another direction, Wang *et al.* utilized a layer-by-layer assembly (LbL) technique to fabricate three different membranes (M^0 , M^- , and M^+), exhibiting neutral, negative, and positive charges at physiological pH 7.4.¹⁴⁹ These membranes were fabricated by alternatively assembling three layers of PEI and PAA onto hydrolysed electrospun PAN membrane. The hydrolysis step was carried out to incorporate negatively charged carboxylic groups, promoting the LbL assembly process. Furthermore, three different sizes of PS NPs (50 nm, 100 nm and 500 nm) were chosen to evaluate the removal efficacy of membranes under very low pressure. Among these modified membranes, M^+ membranes showed excellent performance in removing PS NPs of different sizes, with rejection efficiencies of ~99.4% for 500 nm, ~99.3% for 100 nm, and ~89.9% for 50 nm, while maintaining high flux. It was reported that the removal of PS NPs was primarily governed by electrostatic interactions rather than pore-size exclusion. However, M^- and M^0 membranes had limited rejection efficiency due to their similar or neutral surface charge in connection to PS NPs. Additionally, these membranes successfully retained bacterial contaminants like *E. coli* and *S. aureus* during filtration, which was attributed to smaller pore size of membranes. Thus, the



multifunctional nature of M^+ membrane presents them as a promising alternative for addressing water pollution by NPs.¹⁴⁹

Recently, creating eco-friendly materials with advanced 3D printing technology has paved the way for developing tailored water filtration systems, notably beneficial in regions facing clean water scarcity. A persistent challenge in sustainable water treatment is the need of multifunctional, durable, reusable, and high-flux filtration solutions. In this regard, 3D printing has emerged as an efficient technique which has revolutionized design, prototyping, and manufacturing.¹⁵⁰ Flexibility of 3D printing facilitates the designing of complex shapes and customized structures, permitting the development of membranes that are tailored to meet specific requirements of wastewater treatment.¹⁵¹ Considering the advantages of 3D printing, Fijoł *et al.* constructed fully bio-based and biodegradable polylactic acid (PLA)-based composites water filters via fused deposition modelling (FDM) 3D printing.¹⁵² PLA filters reinforced with TEMPO-oxidized cellulose nanofibers (TCNF) and chitin nanofibers (ChNF) resulted in improved water throughput and mechanical strength as compared to pristine PLA. The biocomposite filters were 3D printed in cylindrical as well as hourglass geometries with varying, multiscale pore architectures. In addition to their structural benefits, the filters exhibited significant adsorption capacity for Cu^{2+} ions (234 and 208 mg/g_{NF} for TCNF and ChNF-reinforced filters, respectively), and PS MPs (50-100 μm) removal from laundry water (54% for TCNF, and 35% for ChNF-reinforced filters). Moreover, metal ion adsorption was mainly governed by electrostatic interactions, while MPs removal was owing to size exclusion and physical bonding to the filter surface. Other than that, PLA-based composite water filters demonstrated recyclability upto multiple times.¹⁵² To the best of our knowledge, only one literature report is available on 3D printed filters for MPs removal,



emphasizing the need for further research and development to unlock their full potential in real-world wastewater treatment applications.

8. Comparative performance metrics

An extensive literature survey demonstrated that several materials, including hydrogels, electrospun fibers and sponges, have already been reported in literature for the removal of MPs. Here, we have compared and summarized the recent examples of hydrogels, sponges and electrospun fibers based upon their maximum removal efficiency and maximum adsorption capacity (**Table 2**). In addition to MPs removal, some polymer-based materials have shown good potential to remove NPs based on size exclusion mechanism and electrostatic interactions among the oppositely charged surfaces. These examples have also been included in **Table 2** as degradation of MPs in surrounding medium over time may lead to the formation of NPs, which are also hazardous like MPs due to their small size.

It should be noted that although the electrospun fibers have shown significant potential to remove MPs from the contaminated wastewater, still, they are rarely employed on industrial-scale wastewater treatment plants due to their relatively higher cost in comparison to the hydrogels and sponges. Moreover, despite the growing interest of utilizing polymeric systems in biological and chemical approaches for MPs removal, this area remains less explored than the conventional physical adsorption and filtration systems. This might be due to the difficulty of integrating catalytic and biological functionalities into polymeric matrices while maintaining sufficient permeability, mechanical stability, and long-term operational performance. The biological treatment process using enzyme-functionalized hydrogels usually exhibit limited environmental



stability, slow degradation kinetics, pH sensitivity, temperature variations, and biofouling-related performance decline, and hence they are rarely explored.



Table 2: Comparative analysis of different materials used for the removal of MPs

| Material Used | Type of matrix | Synthesis method | Type of microplastic removed | Size range of targeted MPs | Surface charges on the adsorbent | Pore/ mesh size of the adsorbent | Maximum removal efficiency (%) | Maximum adsorption capacity (mg/g) | Removal mechanism and remarks | Ref. |
|---|----------------|---|------------------------------|----------------------------|----------------------------------|----------------------------------|--------------------------------|------------------------------------|--|------|
| Lignin/poly(vinyl alcohol) hydrogel | Hydrogel | Functionalized of lignin through phenolization and ammoniation | Polystyrene | 5 μm | 12 mV to 25 mV | 23.77 nm | 97.9 | 288.6 | Adsorption | 108 |
| | | | Polyamide | | | | 99.7 | | | |
| ChNFs/ lignin composite hydrogel | Hydrogel | Chemical crosslinking of epichlorohydrin onto the chitin nanofibrils and quaternized Kraft lignin | Polystyrene | 166.5 nm | $\sim + 12.1$ mV | > 100 μm | 93.7 | 1790.8 | Electrostatic interactions and π - π interactions | 153 |
| Polydopamine-modified sodium alginate hydrogel | Hydrogel | Ionic gelation in combination with in situ polydopamine coating/polymerization | Polystyrene | 0.1 to 1.5 μm | -19.63 mV | 200 nm to 10 μm | 99.6 | 154.57 | Chemical adsorption, π - π interactions and electrostatic interactions | 90 |
| Gelatin-sodium alginate aerogel | Hydrogel | Chemical crosslinking of gelatin and sodium alginate with glutaraldehyde | Polystyrene | 50 μm | - | 1–10 μm | 90 | - | Adsorption, hydrogen bonding, ionic interactions and physical | 154 |





| | | | | | | | | | | |
|--|----------|---|---|----------------------------|-------|----------------|-------|--------|--|----------------|
| | | | | | | | | | interception within the aerogel's 3D-network | |
| Taro stem-sourced cellulose/polypyrrole hybrid aerogel | Hydrogel | Chemical crosslinking and freeze-drying | Polystyrene | 200 nm to 2000 nm | - | 6.45 nm | 91.55 | 818.06 | Physical entrapment, hydrogen bonding, electrostatic interactions, and π - π interactions | ¹⁵⁵ |
| Melamine sponges modified with mussel-inspired polydopamine | Sponge | Surface functionalization of melamine sponge with PDA-PEI coating | Micro and nanoplastics | 10 μ m | - | 160.85 μ m | 90 | 302 | electrostatic attractions, hydrophobic interactions, and π - π stacking with aromatic polymers | ¹⁵⁶ |
| MOF-based superhydrophobic sponge | Sponge | auto-polymerization of polydopamine followed by coprecipitation of Ni-MOF and PDA-modified sponge | Polystyrene, acrylonitrile-butadiene-styrene, Polyvinyl chloride, polyethylene, | 6.5 μ m to 150 μ m | 65 mV | - | 95.1 | 67.4 | Electrostatic interactions, Capillary force of inner pores, hydrogen bonding, hydrophobic | ¹⁵⁷ |

| | | | | | | | | | | |
|---|------------------------------|--|---|----------------------------|---------------------|---|-------|--------|--|----------------|
| | | | and polypropylene | | | | | | interactions, and p- π conjugation | |
| Chitin-cellulose nanofibers nanosponges | Electrospun nanofiber Sponge | controlled chemical modifications of starch and pectin followed by freeze-thaw technique to design ChCNFs nanosponge | Polystyrene | 1 μ m | - | - | 93.07 | 116.34 | Intraparticle diffusion mechanism | ¹⁵⁸ |
| Cu/Co-LDHs-based superhydrophobic sponge | Sponge | PDA coating, in situ growth of CuCo-LDHs, and HDTMS surface modification on a pretreated melamine sponge. | Polyethylene and polypropylene | 6.5 μ m to 150 μ m | 62 mV | - | 100 | 56.2 | Electrostatic attractions, and hydrogen bonding through Intraparticle diffusion mechanisms | ¹⁵⁹ |
| Wood derived cellulose sponges | Sponge | Delignification of Balsa wood and sulfonation modification of wood derived cellulose sponges | Amine-modified polystyrene microspheres | 500 nm | -8.5 mV to -94.4 mV | - | 88.8 | 586.95 | electrostatic attraction, hydrogen bonding and <i>Van der Waals</i> forces | ¹⁶⁰ |





| | | | | | | | | | | |
|---|-------------------|--|---------------------------|-------------------|---|--|------|------|---|----------------|
| Loofah plant—derived biodegradable superhydrophobic sponge | Sponge | Dip-coating method | Polystyrene microplastics | 5 μm | - | - | 99.9 | 569 | Monolayer and multilayer adsorption mechanisms | ¹⁶¹ |
| Hardwood vessel-inspired chitosan-based sponge | Sponge | Directional freeze-casting of a chitosan solution followed by glutaraldehyde vapor crosslinking, neutralization, and freeze-drying | Polystyrene | 1 μm | - | - | 94.9 | 0.26 | Adsorption mechanism through electrostatic bonding and p- π interactions | ¹³³ |
| Bio-based electrospun polyamide membrane | Electrospun fiber | Melt polycondensation of hexamethylenediamine–azelaic acid, followed by electrospinning and emulsion polymerization | Polystyrene | 0.3 μm | - | 0.55 μm to 1.14 μm | 99.8 | - | Surface filtration mechanism with 123% high initial permeability, 99.9% separation efficiency for oil-water emulsion with a high flux of 5345 $\text{L m}^{-2} \text{h}^{-1}$, significant antifouling property of the | ¹⁴² |

| | | | | | | | | | | |
|--|-------------------|--|---|-----------------|--------|-------------------|------|---|--|----------------|
| | | | | | | | | | membrane upto 10 cycles | |
| Electrospun polyurethane nanofiber membrane | Electrospun fiber | surfactant-free emulsion polymerization followed by electrospinning | Acrylonitrile butadiene styrene, polystyrene and polymethylmethacrylate | 90 nm to 825 nm | -42 mV | 1309 nm | 93% | - | Cake formation, intermediate blocking, and standard blocking fouling mechanisms, 8163 L m ⁻² h ⁻¹ pressure-driven water flow and 793 L m ⁻² h ⁻¹ gravity-driven water flux, reusability up to 10 filtration cycles | ¹⁴⁷ |
| Polyvinyl alcohol nanofibrous membrane | Electrospun fiber | Electrospinning 7% and 10 wt% aqueous PVA solutions at 20 kV using a rotary drum collector under optimized flow rate and spinning conditions | Polyethylene and polystyrene | <50 μm | - | 169 nm and 113 nm | 77.3 | - | Size exclusion mechanism 109 ± 1.67 L m ⁻² min ⁻¹ membrane flux at 5 psi, reduced fouling time | ¹⁴⁸ |





| | | | | | | | | | | |
|---|-------------------|--|-------------|-----------------|--------------------|---|------|---|---|-----|
| | | | | | | | | | with 75% ± 3.5% efficiency after 5 round of filtration cycles | |
| Electrospun polyacrylonitrile membrane | Electrospun fiber | Electrospinning fabrication of PAN nanofibrous membrane followed by layer-by-layer (LbL) surface modification using PEI/PAA polyelectrolyte assembly | Polystyrene | 50 nm to 500 nm | + 18 mV to - 60 mV | - | 89.9 | - | Electrostatic attraction-driven adsorption and low pressure driven by low pressure, 1452.4 Lm ⁻² ·h ⁻¹ highest flux of the membrane in pure water, promising fouling resistances to bacteria, recyclability of the membrane up to two filtration cycles | 149 |

| | | | | | | | | | | |
|--|--------------------------|---|------------------------------|--------------------|---|-------------------|-------|-------|---------------------------|-----|
| Chitosan/ polyethylene oxide Nanofiber Sponge | Electrospun fiber sponge | Electrospinning, followed by Neutralization of Chitosan-polyethylene oxide Nanofiber and preparation of Chitosan NF Sponges | Poly(ethylene terephthalate) | 48.7 μm | - | 130 μm | 99.46 | 335.3 | - | 132 |
| Electrospun polyacrylonitrile membrane | Electrospun fiber | Electrospinning and subsequently surface-modified via layer-by-layer assembly | Polystyrene | 50 nm to 500 nm | - | - | 89.9 | - | Electrostatic attractions | 149 |



9. Management strategies

The management of MPs contamination for safe environment requires multidimensional approach including the involvement of public, industries, government, and international organizations. In this direction, the first step is to reduce overall plastic consumption. Furthermore, the public awareness programs should be conducted to educate people regarding negative impacts of MPs on our environment and the significance of reducing plastic usage. This can be done by conducting outreach activities in schools, colleges, and community organizations. It has been found that the main source of MPs production is single-use plastic (SUP).¹⁶² To eliminate SUP from environment, people should be encouraged to utilize reusable containers, bottles, and bags.

Further, government, industries, scientists, and individuals must work together in a team to reduce plastic trash, improve plastic waste management, and create new alternatives. Government may consider monitoring and limiting the usage of MPs in cosmetics, cleansing agents, and other personal care products. Further, modern filtration technologies may be implemented to upgrade existing wastewater treatment facilities to eliminate MPs prior to their discharge into waterbodies.¹⁶³⁻¹⁶⁴ Additionally, the enhanced producer responsibility can be implemented.¹⁶⁵ Furthermore, government should encourage industry to work on sustainable practices such as minimizing plastic-based packaging and increasing their efforts for plastic waste management. This may be done by rewarding organizations that take significant steps in this direction and invest in eco-friendly alternatives.

Waste management follows five Rs hierarchy: reduce, reuse, recycle, redesign, and recover.¹⁶⁶ Generation of MPs can be reduced by minimizing the production of plastic. Reusing and recycling plastic products further helps in reducing the amount of plastic debris.¹⁶⁷ Further, sustainable management of plastic wastes can also be achieved via upcycling which provides other



value added materials.¹⁶⁸ A portion of the energy can be recovered from plastic by incineration and approaches like co-fuelling of kilns, offering a practical route to achieving reasonable energy efficiency.¹⁶⁹ These strategies are advantageous as compared to landfill disposal, as they allow energy recovery from plastic to some extent.¹⁶⁶

Moreover, the molecular redesign of plastics has emerged as a new approach in green chemistry, and should be integrated into the design and life cycle analysis of plastics. In line with this, some alternatives can be used to minimize the usage of excessive chemicals in plastic manufacturing, for example, citrates can be used as a substitute for synthetic plasticizers.¹⁶⁶ Similarly, zeolites can be employed to produce sustainable plastics from bio-based feedstock.¹⁶⁵ Zeolites can turn lactic acid into lactide, which is a key ingredient for making biodegradable plastics like PLA.¹⁶⁵ These innovations not only lower the environmental footprint of plastic production but also support the transition towards a circular and more sustainable materials economy.

10. Challenges and future perspectives

MPs have been globally recognized as a major pollutant leading to a surge in scientific efforts for developing strategies to handle MPs pollution. In this regard, hydrogels have recently emerged as a potential candidate due to their unique swelling properties allowing them to adsorb MPs on their surface and within the porous network, thus removing MPs from water. However, for effective application, hydrogels must be optimized to enhance their adsorption efficiency and mechanical robustness under diverse environmental conditions. It is also crucial to investigate how these hydrogels interact with MPs, specifically under different pH, temperature, and saline conditions. In future, studies should be performed to understand molecular-level interactions focusing on the



effects of charge, hydrophobicity, surface chemistry, and other physicochemical properties of hydrogels on the adsorption process.

Further, attention should be given on tuning the chemical structure of polymeric hydrogels, sponges, and electrospun fibers for selectivity towards specific type of MPs. Incorporation of stimuli responsive feature in these adsorbent materials may further help in easy capture and removal of MPs.¹²⁶ In addition to adsorption of MPs, the overall composition of these materials should be chosen in such a way that degradation of MPs can also be achieved. This direction can be explored by embedding photocatalytic nanomaterials inside the polymeric matrix.¹²² Moreover, sustainability, biodegradability, reusability, processability, scalability, and reduced secondary pollution are important criteria for analyzing the practical applicability of these materials. Hence, a thorough analysis of the existing materials in these aspects is the need of the hour.

It may be noted that the MPs are comparably easier to be detected, monitored, and removed using the existing analytical and separation techniques due to their micron-scale dimensions. However, the NPs pose a significant challenge even with the existing techniques due to their smaller size. Additionally, NPs exhibit more ecotoxicological impacts and can easily penetrate through the cell membranes as compared to MPs. Due to large surface to volume ratio, NPs can exhibit higher uptake of toxic chemicals as compared to the same mass of MPs, and may produce Trojan horse effect.¹⁷⁰ Although, the advanced characterization methods such as electron microscopy, Raman spectroscopy, dynamic light scattering analysis, Fourier-transform infrared spectroscopy and thermal analysis have been explored for quantification and detection of NPs, however, their precise identification and monitoring remain a major challenge, and requires further technological advancements.



Effective utilization of the aforementioned adsorbent materials on large scale is another hurdle. Although lab-scale results are promising, scaling up to larger operations demands cost effectiveness, easy material accessibility, and broad applicability of a single system. Moreover, strategies for incorporating these materials into filters, membranes, or reactors utilized in municipal and industrial water treatment should be investigated to facilitate their large-scale utilization. Further, exploration of AI in the context of wastewater treatment still remains in nascent stage. Application of AI models in this context may help in automation of such water treatment facilities resulting in easy and low-cost operations.¹⁷¹⁻¹⁷² This can also help in predicting the removal efficiency of hydrogels, sponges, and electrospun fibers-based materials under complex and continuously varying waste water conditions.¹⁷³

Finally, the researchers should concentrate on fabricating biodegradable hydrogels, sponges, and electrospun fibers-based materials that can be readily disposed of or repurposed at the end of their lifecycle, thereby minimizing secondary environmental pollution. Considering *waste-to-wealth* approach, different waste resources or biomass can be employed for fabrication of these materials. Additionally, new approaches must be developed to reprocess used materials into other useful value-added materials that can be further utilized for the benefit of the society. Moreover, long-term ecological and biological impact of employing these materials for MPs and NPs extraction should also be evaluated along with their life cycle analysis.

11. Conclusion

MPs pollution has become an alarming environmental concern due to the widespread applicability of plastic products and adversely impact both terrestrial and aquatic ecosystems. This review highlights the importance of different removal methods and recently explored materials. Distinct



studies represented the effectiveness of the adsorption method for MPs removal. In this regard, polymeric hydrogels, sponges, and electrospun fibers have attracted a significant interest as a potential adsorbent material owing to their highly porous architecture which provides more surface area to capture MPs and NPs. Recent laboratory studies have shown > 99% MPs removal efficiencies using polydopamine-modified sodium alginate hydrogel. Similarly, Loofah plant—derived biodegradable superhydrophobic sponge have shown > 99.9% MPs removal potential. Further, in some cases, the incorporation of different additives in these materials improves their mechanical strength and helps in shortening the adsorption time, while also offering the capability of MPs degradation. However, the research on polymeric hydrogels, sponges, and electrospun fibers for MPs and NPs removal still remains in its nascent stage. Continued research and innovation in these materials are essential for optimizing their usage and ensuring their economic feasibility to take a step further for moving towards global sustainable development goals.

Abbreviations

AA: Acrylic acid; ABS: Acrylonitrile butadiene styrene; AM: Acrylamide; AOPs: Advanced oxidation processes; BC: Bacterial cellulose; BGCS: Double crosslinked chitosan-based sponges; Ch: Chitin; ChCN: Chitin/O-C₃N₄; ChGO: Graphene oxide-incorporated chitin; ChGO-CL: Chitin/GO/carboxymethyl cellulose; ChGO-CS: Chitin/GO/chitosan; ChNF: Chitin nanofibers; ChPANIs: Chitin-PANIs sponge; CNF: Cellulose nanofiber; CS: Chitosan; CSNF: Chitosan nanofiber sponges; Cu-POM: Copper substituted polyoxometalate; FDM: Fused deposition modelling; Fe³⁺@PS: Iron doped polystyrene microplastics; GA: Glutaraldehyde; GO: Graphene oxide; GO₅/CS/GP: Graphene oxide/chitin/genipin sponges; GOMt: Graphene oxide-montmorillonite; GP: Genipin; IPNs: Interpenetrating networks; LbL assembly: Layer-by-layer



assembly; LG-GH-PVA: lignin/epichlorohydrin/polyvinyl alcohol; MA: Methacrylic acid; MB: Methylene blue; MBA: *N, N'*-methylene bisacrylamide; MO: Methylene orange; MOFs: Metal-organic frameworks; MPs: Microplastics; NIPAM: N-isopropylacrylamide; NPs: Nanoplastics; NVCL: N-vinyl caprolactam; NVP: N-vinylpyrrolidone; PA: Polyamide; PAA: Polyacrylic acid; PAHs: Polycyclic aromatic hydrocarbons; PAN: Polyacrylonitrile; PANI: Polyaniline; PC: Polycarbonate; PCBs: Polychlorinated biphenyls; PDA: Polydopamine; PE: Polyethylene; PEG: Polyethylene glycol; PEI: Polyethylene imine; PA@EFMs: Polyamide electrospun fibers-based membranes; PEI@PDA: Polyethyleneimine and polydopamine copolymer; PET: Polyethylene terephthalate; pGel@IPN: Cu-POM infused triple interpenetrating network hydrogel; PGT membrane: Polyurethane/graphene oxide-montmorillonite electrospun composite membrane; PLA: Polylactic acid; PMMA: Polymethyl methacrylate nanoplastics; PNIPAM: Poly(N-isopropyl acrylamide); PP: Polypropylene; PS: Polystyrene; PS-COOH: Carboxylate-functionalized polystyrene; PS-NH₂: Amine-functionalized polystyrene; PU: Polyurethane; PVA: Polyvinyl alcohol; PVC: Polyvinyl chloride; PVDF: Polyvinylidene fluoride; ROS: Reactive oxygen species; SEM: Scanning Electron Microscopy; SUP: Single-use plastic; TCNF: TEMPO-oxidized cellulose nanofibers.


Author information

Corresponding Author

Garima Agrawal – School of Chemical Sciences and Advanced Materials Research Centre, Indian Institute of Technology Mandi, Mandi – 175075, Himachal Pradesh, India.

<https://orcid.org/0000-0002-3391-2378>; E-mail: garima@iitmandi.ac.in

Authors



Ankita Dhiman – School of Chemical Sciences and Advanced Materials Research Centre, Indian Institute of Technology Mandi, Mandi – 175075, Himachal Pradesh, India. <https://orcid.org/0000-0002-9906-6047>

Amit Kumar Sharma – Department of Chemistry, University Institute of Sciences, Chandigarh University, Mohali 140413, Punjab, India; University Centre for Research & Development, Chandigarh University, Mohali 140413, Punjab, India. <https://orcid.org/0000-0001-7573-8526>

Bartholomew Richard – School of Chemical Sciences and Advanced Materials Research Centre, Indian Institute of Technology Mandi, Mandi – 175075, Himachal Pradesh, India. <https://orcid.org/0000-0002-8388-3181>

Priyanka Bharti – School of Chemical Sciences and Advanced Materials Research Centre, Indian Institute of Technology Mandi, Mandi – 175075, Himachal Pradesh, India. <https://orcid.org/0009-0005-0147-7147>

Notes

The authors declare no conflicts of interest.

Acknowledgement

GA acknowledges the financial support from the Anusandhan National Research Foundation ANRF-SERB, India (Grant No. WEA/2023/000001). PB thanks Council of Scientific and Industrial Research (CSIR) for fellowship.

References



1. Huo, E.; Lei, H.; Liu, C.; Zhang, Y.; Xin, L.; Zhao, Y.; Qian, M.; Zhang, Q.; Lin, X.; Wang, C., Jet fuel and hydrogen produced from waste plastics catalytic pyrolysis with activated carbon and MgO. *Science of the Total Environment* **2020**, *727*, 138411.
2. Conti, I.; Simioni, C.; Varano, G.; Brenna, C.; Costanzi, E.; Neri, L. M., Legislation to limit the environmental plastic and microplastic pollution and their influence on human exposure. *Environmental Pollution* **2021**, *288*, 117708.
3. Xiang, Y.; Jiang, L.; Zhou, Y.; Luo, Z.; Zhi, D.; Yang, J.; Lam, S. S., Microplastics and environmental pollutants: Key interaction and toxicology in aquatic and soil environments. *Journal of Hazardous Materials* **2022**, *422*, 126843.
4. Reichelt-Brushett, A., *Marine pollution—monitoring, management and mitigation*. Springer Nature: 2023.
5. Ng, C. H.; Mistoh, M. A.; Teo, S. H.; Galassi, A.; Ibrahim, A.; Sipaut, C. S.; Foo, J.; Seay, J.; Taufiq-Yap, Y. H.; Janaun, J., Plastic waste and microplastic issues in Southeast Asia. *Frontiers in Environmental Science* **2023**, *11*, 1142071.
6. Li, P.; Wang, X.; Su, M.; Zou, X.; Duan, L.; Zhang, H., Characteristics of plastic pollution in the environment: a review. *Bulletin of environmental contamination and toxicology* **2021**, *107* (4), 577-584.
7. Yao, L.; Hui, L.; Yang, Z.; Chen, X.; Xiao, A., Freshwater microplastics pollution: detecting and visualizing emerging trends based on Citespace II. *Chemosphere* **2020**, *245*, 125627.
8. Fakhri, V.; Hamzehlouy, A.; Dehchani, A. J.; Moradi, E.; Dare, M. T.; Jafari, A.; Khonakdar, H. A., Green solutions for blue waters: Using biomaterials to purify water from microplastics and nanoplastics. *Journal of Water Process Engineering* **2024**, *65*, 105854.



9. Bui, X.-T.; Nguyen, P.-T.; Nguyen, V.-T.; Dao, T.-S.; Nguyen, P.-D., Microplastics pollution in wastewater: Characteristics, occurrence and removal technologies. *Environmental Technology & Innovation* **2020**, *19*, 101013.
10. Ghosh, S.; Sinha, J. K.; Ghosh, S.; Vashisth, K.; Han, S.; Bhaskar, R., Microplastics as an emerging threat to the global environment and human health. *Sustainability* **2023**, *15* (14), 10821.
11. Periyasamy, A. P.; Tehrani-Bagha, A., A review on microplastic emission from textile materials and its reduction techniques. *Polymer Degradation and Stability* **2022**, *199*, 109901.
12. Andrady, A. L.; Barnes, P. W.; Bornman, J. F.; Gouin, T.; Madronich, S.; White, C.; Zepp, R. G.; Jansen, M. A., Oxidation and fragmentation of plastics in a changing environment; from UV-radiation to biological degradation. *Science of the Total Environment* **2022**, *851*, 158022.
13. Sutkar, P. R.; Gadewar, R. D.; Dhulap, V. P., Recent trends in degradation of microplastics in the environment: A state-of-the-art review. *Journal of Hazardous Materials Advances* **2023**, *11*, 100343.
14. Sa'adu, I.; Farsang, A., Plastic contamination in agricultural soils: a review. *Environmental Sciences Europe* **2023**, *35* (1), 13.
15. Yang, H.; Yumeng, Y.; Yu, Y.; Yinglin, H.; Fu, B.; Wang, J., Distribution, sources, migration, influence and analytical methods of microplastics in soil ecosystems. *Ecotoxicology and Environmental Safety* **2022**, *243*, 114009.
16. Qaiser, Z.; Aqeel, M.; Sarfraz, W.; Rizvi, Z. F.; Noman, A.; Naeem, S.; Khalid, N., Microplastics in wastewaters and their potential effects on aquatic and terrestrial biota. *Case Studies in Chemical and Environmental Engineering* **2023**, *8*, 100536.



17. Feng, Y.; Tu, C.; Li, R.; Wu, D.; Yang, J.; Xia, Y.; Peijnenburg, W. J.; Luo, Y., A systematic review of the impacts of exposure to micro-and nano-plastics on human tissue accumulation and health. *Eco-Environment & Health* **2023**, *2* (4), 195-207.
18. Garcia, M.; Campen, M., Nanoplastics in the human brain and their change in abundance over time. NATURE PORTFOLIO HEIDELBERGER PLATZ 3, BERLIN, 14197, GERMANY: 2025; Vol. 31, pp 1077-1078.
19. Kaushik, A.; Singh, A.; Gupta, V. K.; Mishra, Y. K., Nano/micro-plastic, an invisible threat getting into the brain. *Chemosphere* **2024**, *361*, 142380.
20. Papac Zjačić, J.; Tonković, S.; Pulitika, A.; Katančić, Z.; Kovačić, M.; Kušić, H.; Hrnjak Murgić, Z.; Lončarić Božić, A., Effect of aging on physicochemical properties and size distribution of PET microplastic: influence on adsorption of diclofenac and toxicity assessment. *Toxics* **2023**, *11* (7), 615.
21. Wang, Y.; Liu, C.; Wang, F.; Sun, Q., Behavior and mechanism of atrazine adsorption on pristine and aged microplastics in the aquatic environment: Kinetic and thermodynamic studies. *Chemosphere* **2022**, *292*, 133425.
22. Luo, H.; Liu, C.; He, D.; Xu, J.; Sun, J.; Li, J.; Pan, X., Environmental behaviors of microplastics in aquatic systems: A systematic review on degradation, adsorption, toxicity and biofilm under aging conditions. *Journal of Hazardous Materials* **2022**, *423*, 126915.
23. Lu, Q.; Zhou, Y.; Sui, Q.; Zhou, Y., Mechanism and characterization of microplastic aging process: A review. *Frontiers of Environmental Science & Engineering* **2023**, *17* (8), 100.
24. Yu, F.; Qin, Q.; Zhang, X.; Ma, J., Characteristics and adsorption behavior of typical microplastics in long-term accelerated weathering simulation. *Environmental Science: Processes & Impacts* **2024**, *26* (5), 882-890.



25. Wang, Q.; Wangjin, X.; Zhang, Y.; Wang, N.; Wang, Y.; Meng, G.; Chen, Y., The toxicity of virgin and UV-aged PVC microplastics on the growth of freshwater algae *Chlamydomonas reinhardtii*. *Science of the Total Environment* **2020**, *749*, 141603.
26. Zha, F.; Shang, M.; Ouyang, Z.; Guo, X., The aging behaviors and release of microplastics: A review. *Gondwana Research* **2022**, *108*, 60-71.
27. Fu, Q.; Tan, X.; Ye, S.; Ma, L.; Gu, Y.; Zhang, P.; Chen, Q.; Yang, Y.; Tang, Y., Mechanism analysis of heavy metal lead captured by natural-aged microplastics. *Chemosphere* **2021**, *270*, 128624.
28. Martinho, S. D.; Fernandes, V. C.; Figueiredo, S. A.; Vilarinho, R.; Moreira, J. A.; Delerue-Matos, C., Laboratory studies about microplastic aging and its effects on the adsorption of chlorpyrifos. *Polymers* **2023**, *15* (16), 3468.
29. Zhuang, J.; Rong, N.; Wang, X.; Chen, C.; Xu, Z., Adsorption of small size microplastics based on cellulose nanofiber aerogel modified by quaternary ammonium salt in water. *Separation and Purification Technology* **2022**, *293*, 121133.
30. Liu, Q.; Khor, S. M., Emerging absorption-based techniques for removing microplastics and nanoplastics from actual water bodies. *TrAC Trends in Analytical Chemistry* **2024**, *170*, 117465.
31. Misra, A.; Zambrzycki, C.; Kloker, G.; Kotyrba, A.; Anjass, M. H.; Franco Castillo, I.; Mitchell, S. G.; Güttel, R.; Streb, C., Water purification and microplastics removal using magnetic polyoxometalate-supported ionic liquid phases (magPOM-SILPs). *Angewandte Chemie International Edition* **2020**, *59* (4), 1601-1605.



32. Tiwari, E.; Singh, N.; Khandelwal, N.; Monikh, F. A.; Darbha, G. K., Application of Zn/Al layered double hydroxides for the removal of nano-scale plastic debris from aqueous systems. *Journal of Hazardous Materials* **2020**, *397*, 122769.
33. Yen, P.-L.; Hsu, C.-H.; Huang, M.-L.; Liao, V. H.-C., Removal of nano-sized polystyrene plastic from aqueous solutions using untreated coffee grounds. *Chemosphere* **2022**, *286*, 131863.
34. Sharma, A. K.; Bharti, P.; Chaudhary, K.; Gupta, D.; Agrawal, G., ZnO@ CoO reinforced pectin-acacia hydrogel for efficient removal of toxic dyes from wastewater. *International Journal of Biological Macromolecules* **2026**, 149986.
35. Liu, X.; Meng, F.; Luo, L., Recent advances in hemoperfusion adsorbents: From material innovations to emerging application systems. *Biomaterials Science* **2026**.
36. Das, T. K.; Basak, S.; Ganguly, S., 2D nanomaterial for microplastic removal: a critical review. *Chemical engineering journal* **2024**, *492*, 152451.
37. Zhang, Z.; Lu, Y.; Zhao, Y.; Cui, L.; Xu, C.; Wu, S., Current Developments in Chitosan-Based Hydrogels for Water and Wastewater Treatment: A Comprehensive Review. *ChemistrySelect* **2025**, *10* (6), e202404061.
38. Delangiz, N.; Aliyar, S.; Pashapoor, N.; Nobaharan, K.; Lajayer, B. A.; Rodríguez-Couto, S., Can polymer-degrading microorganisms solve the bottleneck of plastics' environmental challenges? *Chemosphere* **2022**, *294*, 133709.
39. Yu, F.; Wu, Z.; Wang, J.; Li, Y.; Chu, R.; Pei, Y.; Ma, J., Effect of landfill age on the physical and chemical characteristics of waste plastics/microplastics in a waste landfill sites. *Environmental Pollution* **2022**, *306*, 119366.



40. Malankowska, M.; Echaide-Gorriz, C.; Coronas, J., Microplastics in marine environment: a review on sources, classification, and potential remediation by membrane technology. *Environmental Science: Water Research & Technology* **2021**, *7* (2), 243-258.
41. Burhani, D.; Voet, V. S.; Folkersma, R.; Maniar, D.; Loos, K., Potential of Nanocellulose for Microplastic removal: Perspective and challenges. *Tetrahedron Green Chem* **2024**, *3*, 100045.
42. Cox, K. D.; Covernton, G. A.; Davies, H. L.; Dower, J. F.; Juanes, F.; Dudas, S. E., Human consumption of microplastics. *Environmental science & technology* **2019**, *53* (12), 7068-7074.
43. Vanetti, C.; Broggiato, M.; Pezzana, S.; Clerici, M.; Fenizia, C., Effects of microplastics on the immune system: How much should we worry? *Immunology Letters* **2025**, 106976.
44. Phothakwanpracha, J.; Lirdwitayaprasit, T.; Pairohakul, S., Effects of sizes and concentrations of different types of microplastics on bioaccumulation and lethality rate in the green mussel, *Perna viridis*. *Marine Pollution Bulletin* **2021**, *173*, 112954.
45. Chen, J.; Lei, C.; Xiao, Y.; Zhang, Q.; Shi, S., Impact of microplastics on human health: A critical role of gut microbiota. *Ecotoxicology and Environmental Safety* **2026**, *316*, 120184.
46. Wright, S. L.; Thompson, R. C.; Galloway, T. S., The physical impacts of microplastics on marine organisms: a review. *Environmental Pollution* **2013**, *178*, 483-492.
47. Jaiswal, K. K.; Dutta, S.; Banerjee, I.; Pohrmen, C. B.; Singh, R. K.; Das, H. T.; Dubey, S.; Kumar, V., Impact of aquatic microplastics and nanoplastics pollution on ecological systems and sustainable remediation strategies of biodegradation and photodegradation. *Science of the Total Environment* **2022**, *806*, 151358.
48. Prata, J. C.; Da Costa, J. P.; Lopes, I.; Duarte, A. C.; Rocha-Santos, T., Environmental exposure to microplastics: An overview on possible human health effects. *Science of the Total Environment* **2020**, *702*, 134455.



49. Leslie, H. A.; Van Velzen, M. J.; Brandsma, S. H.; Vethaak, A. D.; Garcia-Vallejo, J. J.; Lamoree, M. H., Discovery and quantification of plastic particle pollution in human blood. *Environment International* **2022**, *163*, 107199.
50. Liu, S.; Guo, J.; Liu, X.; Yang, R.; Wang, H.; Sun, Y.; Chen, B.; Dong, R., Detection of various microplastics in placentas, meconium, infant feces, breastmilk and infant formula: A pilot prospective study. *Science of the Total Environment* **2023**, *854*, 158699.
51. Ragusa, A.; Svelato, A.; Santacroce, C.; Catalano, P.; Notarstefano, V.; Carnevali, O.; Papa, F.; Rongioletti, M. C. A.; Baiocco, F.; Draghi, S., Plasticenta: First evidence of microplastics in human placenta. *Environment International* **2021**, *146*, 106274.
52. Ni, D.; Yu, K.; Yan, N.; Chen, X.; Xie, Q.; Yang, Y.; Jiang, W.; Yang, Y.; Zhang, J.; Ling, X., Characterization of microplastics in human follicular fluid and assessment of their potential impact on mouse oocyte maturation in vitro. *Ecotoxicology and Environmental Safety* **2025**, *291*, 117796.
53. Ribeiro, F.; O'Brien, J. W.; Galloway, T.; Thomas, K. V., Accumulation and fate of nano- and micro-plastics and associated contaminants in organisms. *TrAC Trends in Analytical Chemistry* **2019**, *111*, 139-147.
54. Rahman, A.; Sarkar, A.; Yadav, O. P.; Achari, G.; Slobodnik, J., Potential human health risks due to environmental exposure to nano-and microplastics and knowledge gaps: A scoping review. *Science of the Total Environment* **2021**, *757*, 143872.
55. Shi, C.; Wu, H.; Wang, W.; Zhao, J.; Niu, F.; Geng, J., Microplastic removal from water using modified maifanite with rotating magnetic field affected. *Journal of Cleaner Production* **2024**, *434*, 140111.



56. Poolwong, T.; Seadan, M.; Liu, Y.; Suttiruengwong, S. In *Separation of microplastic particles by flotation with ultrafine bubbles*, AIP Conference Proceedings, AIP Publishing LLC: 2023; p 030010.
57. Joshua, A. M.; Aznir, P. A. D.; Von Lau, E., Understanding microplastic flotation through microbubble-microplastic interactions. *Surfaces and Interfaces* **2025**, *64*, 106399.
58. Jiang, H.; Bu, J.; Bian, K.; Su, J.; Wang, Z.; Sun, H.; Wang, H.; Zhang, Y.; Wang, C., Surface change of microplastics in aquatic environment and the removal by froth flotation assisted with cationic and anionic surfactants. *Water Research* **2023**, *233*, 119794.
59. Chabi, K.; Li, J.; Ye, C.; Kiki, C.; Xiao, X.; Li, X.; Guo, L.; Gad, M.; Feng, M.; Yu, X., Rapid sand filtration for < 10 μm -sized microplastic removal in tap water treatment: Efficiency and adsorption mechanisms. *Science of the Total Environment* **2024**, *912*, 169074.
60. Ahmed, S.; Mofijur, M.; Nuzhat, S.; Chowdhury, A. T.; Rafa, N.; Uddin, M. A.; Inayat, A.; Mahlia, T.; Ong, H. C.; Chia, W. Y., Recent developments in physical, biological, chemical, and hybrid treatment techniques for removing emerging contaminants from wastewater. *Journal of Hazardous Materials* **2021**, *416*, 125912.
61. Komorowska-Kaufman, M.; Marciniak, W., Removal of microplastic particles during municipal wastewater treatment: A current review. *Desalination and Water Treatment* **2024**, *317*, 100006.
62. Duan, X.; Chen, X.; Shi, L.; Cao, Y.; Liang, Y.; Huang, C.; Cao, Y., Functionality-dependent removal efficiency and mechanisms of polystyrene microplastics by a robust magnetic biochar. *Journal of Environmental Chemical Engineering* **2025**, *13* (2), 115509.



63. Ren, A.; Rius-Ayra, O.; Kang, M.; Llorca-Isern, N., Durably Superhydrophobic Magnetic Cobalt Ferrites for Highly Efficient Oil–Water Separation and Fast Microplastic Removal. *Langmuir* **2024**, *40* (41), 21533-21546.
64. Heo, Y.; Lee, E.-H.; Lee, S.-W., Adsorptive removal of micron-sized polystyrene particles using magnetic iron oxide nanoparticles. *Chemosphere* **2022**, *307*, 135672.
65. Yan, L.; Chen, J.; Zhang, Z.; Liu, Z.; Ding, T.; Shi, G., Reduced graphene oxide membrane with small nanosheets for efficient and ultrafast removal of both microplastics and small molecules. *Journal of Hazardous Materials* **2025**, *487*, 137078.
66. Puteri, M. N.; Gew, L. T.; Ong, H. C.; Ming, L. C., Technologies to eliminate microplastic from water: Current approaches and future prospects. *Environment International* **2025**, 109397.
67. Falco, G.; Fenti, A.; Galoppo, S.; Chianese, S.; Musmarra, D.; Cocca, M.; Mallardo, S.; Iovino, P., Promoting removal of polystyrene microplastics from wastewater by electrochemical treatment. *Journal of Water Process Engineering* **2024**, *68*, 106418.
68. Gangadharan, P. G.; Bharti, A.; Mondal, A., Exploring the degradation of polyethylene terephthalate microplastics from water and synthetic marine water by the electrochemical method. *Journal of Water Process Engineering* **2025**, *76*, 108101.
69. Zheng, X.; Zhang, Y.; Chen, L.; Wang, Z., Synergistic coagulation-flocculation using polymeric ferric sulfate and Opuntia Milpa Alta particles for enhanced polystyrene microplastic removal. *Process Safety and Environmental Protection* **2025**, 108061.
70. Sezer, M.; Isgoren, M.; Veli, S.; Topkaya, E.; Arslan, A., Removal of microplastics in food packaging industry wastewaters with electrocoagulation process: Optimization by Box-Behnken design. *Chemosphere* **2024**, *352*, 141314.



71. Hu, J.; Hu, J., Mineralization characteristics and behavior of polyethylene microplastics through ozone-based treatment. *Chemosphere* **2024**, *349*, 140839.
72. Nieto-Sandoval, J.; Ammar, R.; Sans, C., Enhancing nanoplastics removal by metal ion-catalyzed ozonation. *Chemical Engineering Journal Advances* **2024**, *19*, 100621.
73. Sturm, M. T.; Myers, E.; Schober, D.; Korzin, A.; Thege, C.; Schuhen, K., Comparison of AOP, GAC, and novel organosilane-based process for the removal of microplastics at a municipal wastewater treatment plant. *Water* **2023**, *15* (6), 1164.
74. Pacaphol, K.; Aht-Ong, D.; Coughlan, D.; Hoogewerff, J., Oleo-extraction of microplastics using flotation plus sol-gel technique to confine small particles in silicon dioxide gel. *Environmental Science and Pollution Research* **2024**, *31* (51), 61096-61113.
75. Yang, Z.; Wang, H.; Li, Y.; Zhang, G., Efficient photocatalytic degradation of polystyrene microplastics in water over core-shell BiO₂-x/CuBi₂O₄ heterojunction with full spectrum light response. *Journal of Colloid and Interface Science* **2025**, *686*, 327-335.
76. Sharara, A.; Samy, M.; Mossad, M.; Alalm, M. G., Enhanced depolymerization of microplastic debris in water by a hybrid ZnO-based photocatalysis-persulfate activation system. *Journal of Water Process Engineering* **2025**, *72*, 107633.
77. Gupta, T.; Chakraborty, S.; Bhattacharya, S., Application of membrane bioreactor in microplastic and nanoplastic removal from water. In *Membrane Bioreactor Technology: An Innovative Water Treatment Process*, Elsevier: 2026; pp 277-303.
78. Corpuz, M. V. A.; Cairone, S.; Natale, M.; Giannattasio, A.; Iuliano, V.; Grassi, A.; Pollice, A.; Mannina, G.; Buonerba, A.; Belgiorno, V., Sustainable control of microplastics in wastewater using the electrochemically enhanced living membrane bioreactor. *Journal of Environmental Management* **2024**, *370*, 122649.



79. Lv, S.; Cui, K.; Zhao, S.; Li, Y.; Liu, R.; Hu, R.; Zhi, B.; Gu, L.; Wang, L.; Wang, Q., Continuous generation and release of microplastics and nanoplastics from polystyrene by plastic-degrading marine bacteria. *Journal of Hazardous Materials* **2024**, *465*, 133339.
80. Dubey, A. P.; Thalla, A. K., Bioprospecting indigenous bacteria from landfill leachate for enhanced polypropylene microplastics degradation. *Journal of Hazardous Materials* **2025**, *487*, 137139.
81. Yu, X.; Zhang, Y.; Chen, S.; Chen, S.; Wan, C.; Wang, Y.; Zou, L.; Peng, L.; Ye, L.; Li, Q., Study on the degradation efficiency and mechanism of polystyrene microplastics by five kinds of edible fungi. *Journal of Hazardous Materials* **2025**, *492*, 138165.
82. Liu, J.; Zhao, D.; Wu, X.; Wu, D.; Su, N.; Wang, Y.; Chen, F.; Fu, C.; Wang, J.; Zhang, Q., Synergistic dual-defect band engineering for highly efficient photocatalytic degradation of microplastics via Nb-induced oxygen vacancies in SnO₂ quantum dots. *Journal of Materials Chemistry A* **2025**, *13* (6), 4429-4443.
83. Ning, Z.; Duan, X.; Li, Y.; Zhao, X.; Chang, L., Degradation of polyvinyl chloride microplastics via electrochemical oxidation with a CeO₂-PbO₂ anode. *Journal of Cleaner Production* **2023**, *432*, 139668.
84. Zhang, Y.; Fu, S.; Chen, L., Enhanced removal of polystyrene microplastics through coagulation using polyaluminum ferric chloride with *Opuntia Milpa Alta* particles. *Journal of Environmental Chemical Engineering* **2024**, *12* (5), 113802.
85. Gabisa, E. W.; Ratanatamskul, C., Effects of operating conditions on removal of microplastics (PET, PP, PS) from wastewater by electrocoagulation systems and kinetics of chromium removal in the presence of microplastics. *Journal of Water Process Engineering* **2024**, *61*, 105313.



86. Simon, M.; Vianello, A.; Vollertsen, J., Removal of > 10 μm microplastic particles from treated wastewater by a disc filter. *Water* **2019**, *11* (9), 1935.
87. Jiang, H.; Zhang, Y.; Bian, K.; Wang, C.; Xie, X.; Wang, H.; Zhao, H., Is it possible to efficiently and sustainably remove microplastics from sediments using froth flotation? *Chemical engineering journal* **2022**, *448*, 137692.
88. Mani, T.; Frehland, S.; Kalberer, A.; Burkhardt-Holm, P., Using castor oil to separate microplastics from four different environmental matrices. *Analytical Methods* **2019**, *11* (13), 1788-1794.
89. Hanif, M. A.; Ibrahim, N.; Hayazi, N. A.; Dahalan, F. A.; Ali, U. F. M.; Jalil, A. A.; Syafiuddin, A., Enhancement of microplastics and nanoplastics removal via filtration method using surface-engineered palm kernel shell biochar. *Separation and Purification Technology* **2025**, *360*, 130596.
90. Han, M.; Wang, Z.; Xie, Z.; Hou, M.; Gao, Z., Polydopamine-modified sodium alginate hydrogel for microplastics removal: Adsorption performance, characteristics, and kinetics. *International Journal of Biological Macromolecules* **2025**, *297*, 139947.
91. Loo, S. L.; Vásquez, L.; Athanassiou, A.; Fragouli, D., Polymeric hydrogels—a promising platform in enhancing water security for a sustainable future. *Advanced Materials Interfaces* **2021**, *8* (24), 2100580.
92. Yang, D., Recent advances in hydrogels. ACS Publications: 2022; Vol. 34, pp 1987-1989.
93. Duman, O.; Polat, T. G.; Diker, C. Ö.; Tunç, S., Agar/ κ -carrageenan composite hydrogel adsorbent for the removal of Methylene Blue from water. *International Journal of Biological Macromolecules* **2020**, *160*, 823-835.



94. Chaudhary, K.; Sharma, A. K.; Bharti, P.; Agrawal, G., Reduced graphene oxide embedded carrageenan/acacia-based hybrid hydrogel nanocomposite for the efficient entrapment of safranin and methylene blue dyes. *Journal of Molecular Liquids* **2025**, 128718.
95. Aboomeirah, A. A.; Kabil, M. F.; Azzazy, H. M. E.-S., Polyvinyl alcohol-chitosan-polyethylene glycol-glycerol incorporated with Peganum harmala loaded in lipid nanocapsules as an elastic nanocomposite surgical sealant to control bleeding. *International Journal of Biological Macromolecules* **2024**, 280, 135987.
96. Salma-Ancane, K.; Scegljovs, A.; Tracuma, E.; Wychowaniec, J. K.; Aunina, K.; Ramata-Stunda, A.; Nikolajeva, V.; Loca, D., Effect of crosslinking strategy on the biological, antibacterial and physicochemical performance of hyaluronic acid and ϵ -polylysine based hydrogels. *International Journal of Biological Macromolecules* **2022**, 208, 995-1008.
97. Tiwari, H.; Sharma, A. K.; Bharti, P.; Agrawal, G., CuO-integrated hydrogel network of gelatin and gellan gum for the efficient sequestration of rhodamine B and crystal violet. *International Journal of Biological Macromolecules* **2025**, 146016.
98. Huaman, M. A. L.; Vega-Chacón, J.; Quispe, R. I. H.; Negrón, A. C. V., Synthesis and swelling behaviors of poly (2-hydroxyethyl methacrylate-co-itaconic acid) and poly (2-hydroxyethyl methacrylate-co-sodium itaconate) hydrogels as potential drug carriers. *Results in Chemistry* **2023**, 5, 100917.
99. Gao, Y.; Zong, S.; Huang, Y.; Yang, N.; Wen, H.; Jiang, J.; Duan, J., Preparation and properties of a highly elastic galactomannan-poly (acrylamide-N, N-bis (acryloyl) cysteamine) hydrogel with reductive stimuli-responsive degradable properties. *Carbohydrate Polymers* **2020**, 231, 115690.



100. Homma, K.; Chang, A. C.; Yamamoto, S.; Tamate, R.; Ueki, T.; Nakanishi, J., Design of azobenzene-bearing hydrogel with photoswitchable mechanics driven by photo-induced phase transition for in vitro disease modeling. *Acta biomaterialia* **2021**, *132*, 103-113.
101. Sennakesavan, G.; Mostakhdemin, M.; Dkhar, L. K.; Seyfoddin, A.; Fatihhi, S. J., Acrylic acid/acrylamide based hydrogels and its properties-A review. *Polymer Degradation and Stability* **2020**, *180*, 109308.
102. Nasution, H.; Harahap, H.; Dalimunthe, N. F.; Ginting, M. H. S.; Jaafar, M.; Tan, O. O.; Aruan, H. K.; Herfananda, A. L., Hydrogel and effects of crosslinking agent on cellulose-based hydrogels: A review. *Gels* **2022**, *8* (9), 568.
103. Yadav, P.; Singh, S.; Jaiswal, S.; Kumar, R., Synthetic and natural polymer hydrogels: a review of 3D spheroids and drug delivery. *International Journal of Biological Macromolecules* **2024**, *280*, 136126.
104. Kaith, B. S.; Singh, A.; Sharma, A. K.; Sud, D., Hydrogels: synthesis, classification, properties and potential applications—a brief review. *Journal of Polymers and the Environment* **2021**, *29* (12), 3827-3841.
105. Mondal, S.; Baghel, K.; Cho, S.; Lim, H.; Lee, J., Efficient removal of amine-modified polystyrene nanoplastics utilizing poly (N-isopropylacrylamide)-sodium carboxymethyl cellulose hydrogel beads: Parametric optimization and mechanistic insights. *Separation and Purification Technology* **2025**, *363*, 132035.
106. Sharma, A. K.; Kaith, B. S.; Chandel, K.; Singh, A., Chemically modified chitosan-sodium alginate as chemo-sensor adsorbent for the detection of picric acid and removal of biebrich scarlet. *International Journal of Biological Macromolecules* **2020**, *147*, 582-594.



107. Gutierrez, A. M.; Frazar, E. M.; X. Klaus, M. V.; Paul, P.; Hilt, J. Z., Hydrogels and hydrogel nanocomposites: enhancing healthcare through human and environmental treatment. *Advanced healthcare materials* **2022**, *11* (7), 2101820.
108. Li, X.; Xia, Q.; Leng, Y.; Cai, X.; Nie, D., Lignin/Poly (vinyl alcohol) Hydrogel for Detecting and Effectively Removing Microplastics. *Langmuir* **2025**.
109. Maldonado, N.; Amo-Ochoa, P., Advances and novel perspectives on colloids, hydrogels, and aerogels based on coordination bonds with biological interest ligands. *Nanomaterials* **2021**, *11* (7), 1865.
110. Khan, F.; Atif, M.; Haseen, M.; Kamal, S.; Khan, M. S.; Shahid, S.; Nami, S. A., Synthesis, classification and properties of hydrogels: Their applications in drug delivery and agriculture. *Journal of Materials Chemistry B* **2022**, *10* (2), 170-203.
111. Munyiri, C.; Madivoli, E.; Kisato, J.; Gichuki, J.; Kareru, P., Biopolymer based hydrogels: crosslinking strategies and their applications. *International Journal of Polymeric Materials and Polymeric Biomaterials* **2025**, *74* (7), 625-640.
112. Grosjean, M.; Guth, L.; Déjean, S.; Paniagua, C.; Nottelet, B., Dynamic and Degradable Imine-Based Networks for 3D-Printing of Soft Elastomeric Self-Healable Devices. *Advanced Materials Interfaces* **2023**, *10* (17), 2300066.
113. Mredha, M. T. I.; Na, J. Y.; Seon, J.-K.; Cui, J.; Jeon, I., Multifunctional poly (disulfide) hydrogels with extremely fast self-healing ability and degradability. *Chemical engineering journal* **2020**, *394*, 124941.
114. He, L.; Fullenkamp, D. E.; Rivera, J. G.; Messersmith, P. B., pH responsive self-healing hydrogels formed by boronate–catechol complexation. *Chemical Communications* **2011**, *47* (26), 7497-7499.



115. Sun, C.; Jia, H.; Lei, K.; Zhu, D.; Gao, Y.; Zheng, Z.; Wang, X., Self-healing hydrogels with stimuli responsiveness based on acylhydrazone bonds. *Polymer* **2019**, *160*, 246-253.
116. Hosseinzadeh, B.; Ahmadi, M., Degradable hydrogels: Design mechanisms and versatile applications. *Materials Today Sustainability* **2023**, *23*, 100468.
117. Wu, Y.; Liu, J.; Hu, R.; Wang, J.; Cai, X.; Wu, W.; Song, X.; Zhuge, C.; Huang, M.; Xie, H., From weak to strong: the construction of dynamic reversible hydrogen bond in polyaspartic acid double network hydrogel. *Separation and Purification Technology* **2025**, 133023.
118. Shahi, S.; Roghani-Mamaqani, H.; Talebi, S.; Mardani, H., Stimuli-responsive destructible polymeric hydrogels based on irreversible covalent bond dissociation. *Polymer Chemistry* **2022**, *13* (2), 161-192.
119. Rumon, M. M. H., Advances in cellulose-based hydrogels: tunable swelling dynamics and their versatile real-time applications. *RSC advances* **2025**, *15* (15), 11688-11729.
120. Iskandarani, S.; Campos, L. C.; Saikaly, P. E.; Busquets, R., Hybrid Wastewater Treatment: Efficiency and Challenges in Microplastic Removal. *ACS ES&T Water* **2026**.
121. Patel, T.; Lata, R.; Arikibe, J. E.; Rohindra, D., Towards sustainable microplastic cleanup: Al/Fe ionotropic chitosan hydrogels for efficient PET removal. *Environmental Monitoring and Assessment* **2025**, *197* (3), 228.
122. Dutta, S.; Misra, A.; Bose, S., Polyoxometalate nanocluster-infused triple IPN hydrogels for excellent microplastic removal from contaminated water: detection, photodegradation, and upcycling. *Nanoscale* **2024**, *16* (10), 5188-5205.
123. Li, X.; Xia, Q.; Leng, Y.; Cai, X.; Nie, D., Lignin/Poly (vinyl alcohol) Hydrogel for Detecting and Effectively Removing Microplastics. *Langmuir* **2025**, *41* (25), 16506-16518.




124. Leppänen, I.; Lappalainen, T.; Lohtander, T.; Jonkergouw, C.; Arola, S.; Tammelin, T., Capturing colloidal nano-and microplastics with plant-based nanocellulose networks. *Nature Communications* **2022**, *13* (1), 1814.
125. Yi, X.; Zhou, R.; Liu, L.; Xu, S.; Sun, H.; Ogino, K.; Fan, Y., Preparation of nanochitin hydrogels via ice templated chemical/physical crosslinking for microplastic removal. *International Journal of Biological Macromolecules* **2025**, 144806.
126. Guo, Q.; Liu, Y.; Liu, J.; Wang, Y.; Cui, Q.; Song, P.; Zhang, X.; Zhang, C., Hierarchically structured hydrogel actuator for microplastic pollutant detection and removal. *Chemistry of Materials* **2022**, *34* (11), 5165-5175.
127. Sun, C.; Wang, Z.; Chen, L.; Li, F., Fabrication of robust and compressive chitin and graphene oxide sponges for removal of microplastics with different functional groups. *Chemical engineering journal* **2020**, *393*, 124796.
128. Sun, C.; Wang, Z.; Zheng, H.; Chen, L.; Li, F., Biodegradable and re-usable sponge materials made from chitin for efficient removal of microplastics. *Journal of Hazardous Materials* **2021**, *420*, 126599.
129. Zhu, Z.; Wu, X.; Wang, Z., Effect of polyaniline dispersibility in chitin sponge matrix controlled by hydrophilicity on microplastics adsorption. *International Journal of Biological Macromolecules* **2023**, *253*, 127292.
130. Wu, Y.; Chen, S.; Wu, J.; Liu, F.; Chen, C.; Ding, B.; Zhou, X.; Deng, H., Revivable self-assembled supramolecular biomass fibrous framework for efficient microplastic removal. *Science Advances* **2024**, *10* (48), eadn8662.



131. Ko, M.; Jang, T.; Yoon, S.; Lee, J.; Choi, J.-H.; Choi, J.-W.; Park, J.-A., Synthesis of recyclable and light-weight graphene oxide/chitosan/genipin sponges for the adsorption of diclofenac, triclosan, and microplastics. *Chemosphere* **2024**, *356*, 141956.
132. Risch, P.; Adlhart, C., A chitosan nanofiber sponge for oyster-inspired filtration of microplastics. *ACS Applied Polymer Materials* **2021**, *3* (9), 4685-4694.
133. Xu, J.; Guo, Y.; Tang, C.; Qian, Y.; Guo, C.; Wang, Z.; Li, L., Hardwood vessel-inspired chitosan-based sponge with superior compressibility, superfast adsorption and remarkable recyclability for microplastics removal in water. *Chemical Engineering Journal* **2023**, *475*, 146130.
134. Ma, R.; Feng, Y.; Yu, J.; Zhao, X.; Du, Y.; Zhang, X., Ultralight sponge made from sodium alginate with processability and stability for efficient removal of microplastics. *Environmental Science and Pollution Research* **2023**, *30* (47), 104135-104147.
135. Aziz, S.; Mazhar, A.; Ubaid, A.; Shah, S.; Riaz, Y.; Talha, T.; Jung, D., A comprehensive review of membrane-based water filtration techniques. *Appl Water Sci* *14*: 169. 2024.
136. Tang, X.; Xie, B.; Chen, R.; Wang, J.; Huang, K.; Zhu, X.; Li, G.; Liang, H., Gravity-driven membrane filtration treating manganese-contaminated surface water: flux stabilization and removal performance. *Chemical engineering journal* **2020**, *397*, 125248.
137. Hou, L.; Kumar, D.; Yoo, C. G.; Gitsov, I.; Majumder, E. L.-W., Conversion and removal strategies for microplastics in wastewater treatment plants and landfills. *Chemical engineering journal* **2021**, *406*, 126715.
138. Al-Husaini, I. S.; Al Haddabi, M. H., Recent advances in functionalized electrospun nanofiber membranes for enhanced oily water treatment. *Journal of Environmental Chemical Engineering* **2025**, 115391.



139. Dhiman, A.; Sharma, A. K.; Agrawal, G., Polymer based engineered materials for sustainable agriculture. *ACS Agricultural Science & Technology* **2022**, *2* (4), 693-711.
140. Banitaba, S. N.; Ebadi, S. V.; Salimi, P.; Bagheri, A.; Gupta, A.; Arifeen, W. U.; Chaudhary, V.; Mishra, Y. K.; Kaushik, A.; Mostafavi, E., Biopolymer-based electrospun fibers in electrochemical devices: versatile platform for energy, environment, and health monitoring. *Materials Horizons* **2022**, *9* (12), 2914-2948.
141. Das, K. P.; Chauhan, P.; Staudinger, U.; Satapathy, B. K., Exploring sustainable adsorbents to mitigate micro-/nano-plastic contamination: perspectives on electrospun fibrous constructs, biochar, and aerogels. *Environmental Science: Advances* **2024**.
142. Rist, M.; Greiner, A., Bio-based electrospun polyamide membrane–sustainable multipurpose filter membranes for microplastic filtration. *RSC Applied Polymers* **2024**, *2* (4), 642-655.
143. Khademolqorani, S.; Banitaba, S. N.; Gupta, A.; Poursharifi, N.; Ghaffari, A. A.; Jadhav, V. V.; Arifeen, W. U.; Singh, M.; Borah, M.; Chamanehpour, E., Application scopes of miniaturized MXene-functionalized electrospun nanofibers-based electrochemical energy devices. *Small* **2024**, *20* (24), 2309572.
144. Cui, J.; Li, F.; Wang, Y.; Zhang, Q.; Ma, W.; Huang, C., Electrospun nanofiber membranes for wastewater treatment applications. *Separation and Purification Technology* **2020**, *250*, 117116.
145. Chamanehpour, E.; Thouti, S.; Rubahn, H. G.; Dolatshahi-Pirouz, A.; Mishra, Y. K., Smart nanofibers: Synthesis, properties, and scopes in future advanced technologies. *Advanced Materials Technologies* **2024**, *9* (3), 2301392.



146. Wang, Z.; Crandall, C.; Sahadevan, R.; Menkhaus, T. J.; Fong, H., Microfiltration performance of electrospun nanofiber membranes with varied fiber diameters and different membrane porosities and thicknesses. *Polymer* **2017**, *114*, 64-72.
147. Juraij, K.; Ammed, S. P.; Chingakham, C.; Ramasubramanian, B.; Ramakrishna, S.; Vasudevan, S.; Sujith, A., Electrospun polyurethane nanofiber membranes for microplastic and nanoplastic separation. *ACS Applied Nano Materials* **2023**, *6* (6), 4636-4650.
148. Gopakumar, A. N.; Ccancapa-Cartagena, A.; Bell, K.; Salehi, M., Development of crosslinked polyvinyl alcohol nanofibrous membrane for microplastic removal from water. *Journal of Applied Polymer Science* **2024**, *141* (22), e55428.
149. Wang, R.; Zhang, L.; Chen, B.; Zhu, X., Low-pressure driven electrospun membrane with tuned surface charge for efficient removal of polystyrene nanoplastics from water. *Journal of Membrane Science* **2020**, *614*, 118470.
150. Tijjing, L. D.; Dizon, J. R. C.; Ibrahim, I.; Nisay, A. R. N.; Shon, H. K.; Advincula, R. C., 3D printing for membrane separation, desalination and water treatment. *Applied Materials Today* **2020**, *18*, 100486.
151. Roy Barman, S.; Gavit, P.; Chowdhury, S.; Chatterjee, K.; Nain, A., 3D-printed materials for wastewater treatment. *JACS Au* **2023**, *3* (11), 2930-2947.
152. Fijoł, N.; Aguilar-Sánchez, A.; Ruiz-Caldas, M.-X.; Redlinger-Pohn, J.; Mautner, A.; Mathew, A. P., 3D printed polylactic acid (PLA) filters reinforced with polysaccharide nanofibers for metal ions capture and microplastics separation from water. *Chemical engineering journal* **2023**, *457*, 141153.



153. Jung, S.; Kim, J.; Park, S.; Bang, J.; Yun, H.; Won, S.; Kim, S.; Lim, H.; Kim, S.-G.; Kim, J.-C., Nature-derived hydrogel for microplastic removal. *Advanced Composites and Hybrid Materials* **2025**, *8* (5), 346.
154. Xiang, Q.; Xu, Y.; Hou, J.; Zhang, H.; Lu, Z.; Sun, M.; Wu, C.; Rao, H.; Su, G., Sustainable Gelatin–Sodium alginate aerogel adsorbent for efficient microplastic removal in water. *Chemical Engineering Science* **2025**, 123265.
155. Qiu, W.-p.; Su, H.-z.; Su, H.; Luo, S.-h.; Lai, L.-s.; Zhu, J.-l.; Xu, Z.-l.; Wang, H.; Wen, P., Eco-friendly taro stem-sourced cellulose/polypyrrole hybrid aerogel: An efficient capture strategy for microplastics removal. *Chemical engineering journal* **2025**, 168208.
156. Rezvani, H.; González, V. G.; Majooni, Y.; Yousefi, N., Mussel-inspired Modification of Polymeric Sponges for Selective Removal of Microplastics and Nanoplastics from Water. *Journal of Environmental Chemical Engineering* **2025**, 120459.
157. Chen, X.; Ma, H.; Ji, X.; Han, R.; Pang, K.; Yang, Z.; Liu, Z.; Peng, S., Engineering green MOF-based superhydrophobic sponge for efficiently synchronous removal of microplastics and pesticides from high-salinity water. *Water Research* **2023**, *243*, 120314.
158. Sayadi, M. H.; Nowrouzi, M., Biodegradable sponges made from chitin-cellulose nanofibers for sustainable removal of microplastics from aquatic environment. *Journal of Hazardous Materials Advances* **2025**, *17*, 100564.
159. Peng, S.; Chen, X.; Rong, X.; Ma, H.; Zhao, C.; Pang, K., Fabrication of eco-friendly Cu/Co-LDHs-based superhydrophobic sponge and efficiently synchronous removal of microplastic, dyestuff, and oil. *Journal of Cleaner Production* **2023**, *400*, 136708.



160. Lv, L.; Zhong, W.; Wang, Z., Surface modification of hierarchically porous wood derived cellulose sponges with remarkable compressibility and recyclability for efficient microplastic removal. *Separation and Purification Technology* **2025**, 134943.
161. Ha, T. T. V.; Viet, N. M.; Thanh, P. T.; Quan, V. T., Loofah plant—Derived biodegradable superhydrophobic sponge for effective removal of oil and microplastic from water. *Environmental Technology & Innovation* **2023**, 32, 103265.
162. Singh, S.; Biswas, M. K., Management strategies for single-use plastics: lessons to learn from Indian approach of minimizing microplastic waste. *Environmental Science: Advances* **2023**, 2 (12), 1680-1695.
163. Calero, M.; Godoy, V.; Quesada, L.; Martín-Lara, M. Á., Green strategies for microplastics reduction. *Current Opinion in Green and Sustainable Chemistry* **2021**, 28, 100442.
164. Thacharodi, A.; Hassan, S.; Meenatchi, R.; Bhat, M. A.; Hussain, N.; Arockiaraj, J.; Ngo, H. H.; Sharma, A.; Nguyen, H.; Pugazhendhi, A., Mitigating microplastic pollution: A critical review on the effects, remediation, and utilization strategies of microplastics. *Journal of Environmental Management* **2024**, 351, 119988.
165. Onyena, A. P.; Aniche, D. C.; Ogbolu, B. O.; Rakib, M. R. J.; Uddin, J.; Walker, T. R., Governance strategies for mitigating microplastic pollution in the marine environment: a review. *Microplastics* **2021**, 1 (1), 15-46.
166. Thompson, R. C.; Moore, C. J.; Vom Saal, F. S.; Swan, S. H., Plastics, the environment and human health: current consensus and future trends. *Philosophical transactions of the royal society B: biological sciences* **2009**, 364 (1526), 2153-2166.



167. Singh, N.; Hui, D.; Singh, R.; Ahuja, I.; Feo, L.; Fraternali, F., Recycling of plastic solid waste: A state of art review and future applications. *Composites Part B: Engineering* **2017**, *115*, 409-422.
168. Chen, X.; Wang, Y.; Zhang, L., Recent progress in the chemical upcycling of plastic wastes. *ChemSusChem* **2021**, *14* (19), 4137-4151.
169. Prakash, A.; Palkar, R. R., Co-processing of plastic waste in a cement kiln: a better option. *Environmental Science and Pollution Research* **2023**, *30* (10), 24804-24814.
170. Zhang, Y.; Goss, G. G., The “Trojan Horse” effect of nanoplastics: Potentiation of polycyclic aromatic hydrocarbon uptake in rainbow trout and the mitigating effects of natural organic matter. *Environmental Science: Nano* **2021**, *8* (12), 3685-3698.
171. Safeer, S.; Pandey, R. P.; Rehman, B.; Safdar, T.; Ahmad, I.; Hasan, S. W.; Ullah, A., A review of artificial intelligence in water purification and wastewater treatment: Recent advancements. *Journal of Water Process Engineering* **2022**, *49*, 102974.
172. Kamali, M.; Appels, L.; Yu, X.; Aminabhavi, T. M.; Dewil, R., Artificial intelligence as a sustainable tool in wastewater treatment using membrane bioreactors. *Chemical engineering journal* **2021**, *417*, 128070.
173. Zhao, L.; Dai, T.; Qiao, Z.; Sun, P.; Hao, J.; Yang, Y., Application of artificial intelligence to wastewater treatment: A bibliometric analysis and systematic review of technology, economy, management, and wastewater reuse. *Process Safety and Environmental Protection* **2020**, *133*, 169-182.



Data Availability Statement

View Article Online
DOI: 10.1039/D6LP00029K

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

