



Cite this: *J. Mater. Chem. B*, 2018, 6, 7329

Reversible encapsulations and stimuli-responsive biological delivery from a dynamically assembled cucurbit[7]uril host and nanoparticle guest scaffold†

Santu Sinha,^a Nilanjana Das Saha,^{ab} Ranjan Sasmal,^a Divyesh Joshi,^c Soumya Chandrasekhar,^{ab} Monica Swetha Bosco^{ab} and Sarit S. Agasti^{id} *^{abd}

The positive outcome of any therapeutic molecule requires control over its delivery rate. When delivered without control, administration of large doses is required to stimulate a therapeutic effect, frequently leading to increased toxicity or undesirable side effects. Recent advances introduced “smart” materials that actively release drugs in response to environmental stimuli. Although a variety of endogenous and exogenous triggers are reported, they are either difficult to control or lack tissue penetration depth. We report here a dynamic drug delivery scaffold based on a cucurbit[7]uril (CB[7]) host and benzylammonium functionalized gold nanoparticle (AuNP) guest that utilizes a bioorthogonal small molecule to achieve therapeutic control. In addition to their ability to reach deep tissue, small molecule activation is benefitted by their external controllability. Through cell culture studies we demonstrate that the host–guest supramolecular scaffold provides a nontoxic platform that effectively encapsulates a variety of therapeutic molecules and controls the payload release upon exposure to a high-affinity competitive guest molecule. This study presents a new strategy for controlling drug release rate through the use of competitive interactions of orthogonally presented guest molecules with immediate advantages in dosage control.

Received 17th June 2018,
Accepted 24th September 2018

DOI: 10.1039/c8tb01596a

rsc.li/materials-b

Introduction

The outcome of any therapeutic intervention is directly coupled to the way in which drug molecules or pharmacologically active agents are administered.^{1,2} The administration process controls various important parameters, including pharmacokinetics, drug metabolism and toxicity. The systemic delivery that has been in practice since the inception of drugs is traditionally administered either by an oral or an intravenous route. This standard administration process typically leads to a peak-valley plasma concentration–time profile, leading to adverse effects, especially of a drug with small therapeutic index. In order to maintain drug concentration within the therapeutic window, drug delivery systems (DDSs) were developed.^{3,4} DDSs were engineered to deliver

drugs in response to a stimulus leading to regulated and on-demand drug presentation.^{5–8} Various endogenous approaches (e.g., pH, redox and enzyme) that rely on a specific physicochemical characteristic of the tissue microenvironment were developed.^{9,10} However, the endogenous triggers are difficult to control due to their tremendous variation from one patient to another.¹¹ In addition, for many cases, the target site lacks overexpression of suitable endogenous triggers.⁵ Alternatively, controlled delivery systems that rely on exogenous stimuli, such as light, ultrasound, magnetic field, and temperature, were also employed.¹² Although these exogenous stimuli are easier to control, they lack tissue penetration depth.⁵ In light of these challenges, we set out to develop a delivery system that makes use of a bioorthogonal small molecule to achieve therapeutic control as such stimulus can be controlled externally and has the ability to reach deep tissue.¹³

Supramolecular host–guest chemistry facilitates programmable and controllable engineering of molecular systems through the incorporation of various non-covalent molecular recognition motifs.^{14–16} As they employ weak and reversible non-covalent interactions for their recognition process, supramolecular systems can be engineered to assemble and disassemble spontaneously in response to a range of triggers, including


^a New Chemistry Unit, Jawaharlal Nehru Centre for Advanced Scientific Research (JNCASR), Bangalore, Karnataka 560064, India. E-mail: sagasti@jncasr.ac.in

^b Chemistry & Physics of Materials Unit, Jawaharlal Nehru Centre for Advanced Scientific Research (JNCASR), Bangalore, Karnataka 560064, India

^c Molecular Biology and Genetics Unit, Jawaharlal Nehru Centre for Advanced Scientific Research (JNCASR), Bangalore, Karnataka 560064, India

^d School of Advanced Materials (SAMat), Jawaharlal Nehru Centre for Advanced Scientific Research (JNCASR), Bangalore, Karnataka 560064, India

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8tb01596a

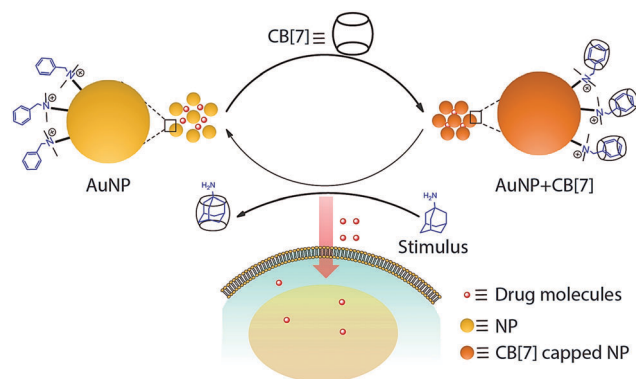

Scheme 1 Dynamic nanoparticle assembly and design of a small molecule stimuli responsive drug delivery system. Assembly of AuNPs driven by CB[7] and disassembly by ADA due to host–guest complexation of CB[7] with ADA. Triggered released of drug molecules from assembly and uptake by the cell.

presentation of complimentary guest molecules.^{17–20} In this communication, we report a dynamic drug delivery scaffold based on a CB[7] host and benzylammonium functionalized AuNP guest with programmed response towards a bioorthogonal small guest molecule (Scheme 1). Among various non-covalent host–guest building blocks, a CB[7] based synthetic receptor was specifically selected for this study due to its high levels of affinity and chemoselectivity, particularly for recognition processes in a biological context.^{21–32} Host–guest recognition between the AuNP guest and CB[7] host forms a non-toxic assembly that is capable of encapsulating drugs as well as various macromolecular therapeutic agents in an efficient manner. This host–guest complex can be disassembled upon presentation of a high affinity competitive guest molecule, such as adamantylamine (ADA). The disassembly process results in triggered release of therapeutic molecules, thereby inducing cell death. We show the ADA concentration dependent change in cell toxicity, effectively correlating the trigger amount with the dose of the released drug. We expect that this study will open up new opportunities for regulating therapeutic systems through the use small molecule triggers, with immediate advantages over dosage control and improved therapeutic effect.

Results and discussion

We designed the guest scaffold by using AuNPs with a core diameter of ~ 2 nm and ~ 5 nm. 2 nm AuNPs were prepared *via* the Brust Schiffrin method whereas a heat induced size evolution method was adopted for preparing 5 nm particles. We used a place exchange reaction to decorate AuNPs with benzylammonium functionalities, which serve as a guest moiety for recognition by CB[7]. Matrix Assisted Laser Desorption/Ionization-Mass Spectrometry (MALDI-MS) was used to verify the chemical functionality on the NP surface (Fig. S3, ESI[†]). Benzylammonium functionalized AuNPs were found to be soluble in water. Transmission electron microscopy (TEM) characterization and Dynamic Light Scattering (DLS) measurement showed

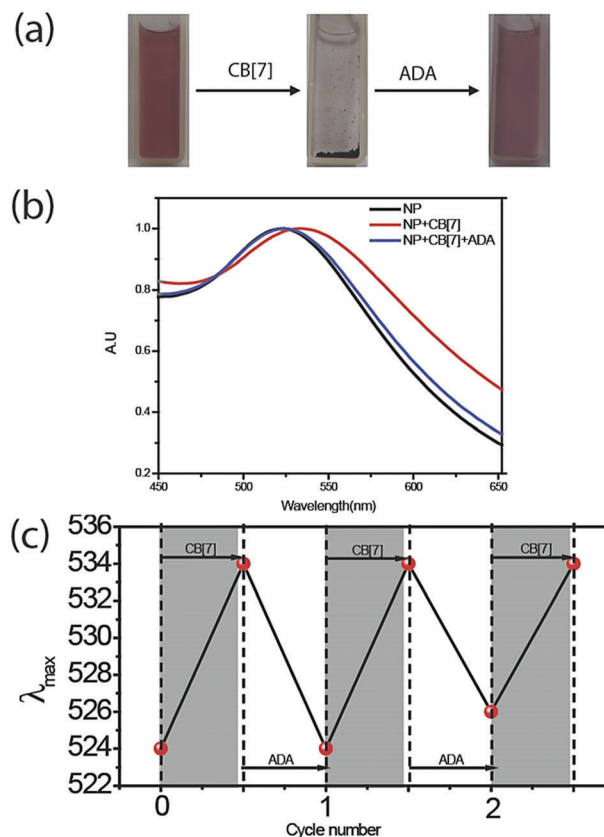


Fig. 1 (a) Reversible assembly of AuNPs. Assembly driven by supramolecular interaction between AuNP and CB[7], and disassembly driven by high affinity guest ADA. 200 nM AuNPs were used to form the assemblies. (b) UV-Vis spectroscopy study of the NP assembly and disassembly process. NP plasmon absorption maximum shifted to the right side in the case of NP + CB[7] and the absorption maximum again came back to the initial stage in the case of NP + CB[7] + ADA. A relatively lower concentration (37 nM) of AuNP was used for this study to achieve smaller and dispersed assembly. (c) Reversible changes in absorption maximum of 5 nm AuNPs by alternative addition of CB[7] and ADA.

that the functionalized AuNPs exist as discrete NPs in solution (Fig. S1 and S4, ESI†).

We used UV-Vis spectroscopy to study the effect of the CB[7] host on the behavior of the NP guest. Monitoring the surface plasmon absorption band is an extremely powerful and sensitive technique to predict the proximity between AuNPs. We observed that surface functionalized NPs were stable in solution for months and the presence of a surface plasmon band was observed at 525 nm for 5 nm AuNPs. However, upon addition of CB[7] into the benzylammonium functionalized AuNP solution, we observed an immediate red shift of the surface plasmon band to 534 nm, indicating formation of AuNP assemblies (Fig. 1a and b). We believe that CB[7] capping of NPs leading to extended NP assembly is an effect of strong interaction between peripheral CB[7] molecules, as observed previously by Kim *et al.* in the case of CB[7] gel formation.³³ To validate that the assembly is driven *via* host-guest mediated interaction between the synthetic receptor, CB[7], and the benzylammonium ligand on the AuNP surface, we used a

The specificity of the assembly towards the ADA trigger was confirmed by employing a photocaged ADA construct (ADAPC, Fig. 2a). In this construct, a photocleavable nitrobenzyl group was attached with the available amine functionality of the ADA moiety to significantly reduce the affinity of ADA towards CB[7]. We observed that incubation of the assemblies with a photocaged version of ADA did not result in any disassembly process, indicating the role of the high-affinity competitive guest to trigger the disassembly process. However, a brief illumination of the sample with 365 nm light resulted in uncaging of ADAPC,

CB[7] mediated *in situ* formation of supramolecular assemblies presents an exciting opportunity for therapeutic encapsulation. We envisioned that during the formation of this supramolecular assembly there would be a generation of void spaces inside the scaffold and these spaces can be effectively utilized to trap a wide range of therapeutically active molecules. First, we used doxorubicin (DOX) as a model system to test the ability of these assemblies to trap small drug molecules. DOX was an ideal choice for this study due to its inherent fluorescence property that helps in quantification of the encapsulation efficiency. For encapsulation studies, AuNPs were first added into a DOX solution with an NP:DOX ratio of 1:10. Subsequently, we formed NP assemblies *via* addition of CB[7]. The assemblies were allowed to settle for a few minutes and the supernatant was collected for quantifying DOX *via* fluorescence measurement. The fluorescence intensity of the supernatant solution was significantly lower when compared against the fluorescence intensity of the incubated solution, indicating successful encapsulation of drug molecules (Fig. S9, ESI[†]). The encapsulation efficiency was estimated to be ~51%. In addition to DOX, we have also tested other drug molecules, like camptothecin (Fig. S10, ESI[†]). In all these cases the assemblies showed abilities to encapsulate the drug molecules irrespective of their diverse structural features. Besides drug molecules, the abilities to encapsulate larger biomolecules were also tested. We observed that the assemblies are capable of encapsulating small DNA molecules as well as proteins (Fig. S11, ESI[†]). Importantly, we also observed that the assembled system can encapsulate enzymes in its active and functional state. For visual demonstration of enzyme encapsulation and catalysis, β -galactosidase was encapsulated into the assembly. We looked at multiple cycles of enzyme activity of the NP assembly using an *o*-nitrophenyl- β -galactoside substrate. During each cycle, after a few minutes of incubation with the substrate, the clear solution turned to yellow, confirming the retention of activity of the encapsulated enzymes (Fig. S12, ESI[†]). Overall, these results indicate the abilities of these assemblies to act as a versatile platform for encapsulation of various biologically active molecules with retention of their activity.

We tested the stimuli responsive release of drug molecules from the supramolecular assemblies using an implant-mimicking device where we used DOX as a model drug molecule. An implant-mimicking device was prepared to separate drug encapsulated nanoparticle assemblies from the released drug molecules. A nitrocellulose membrane (pore diameter of 0.2 μm) was used


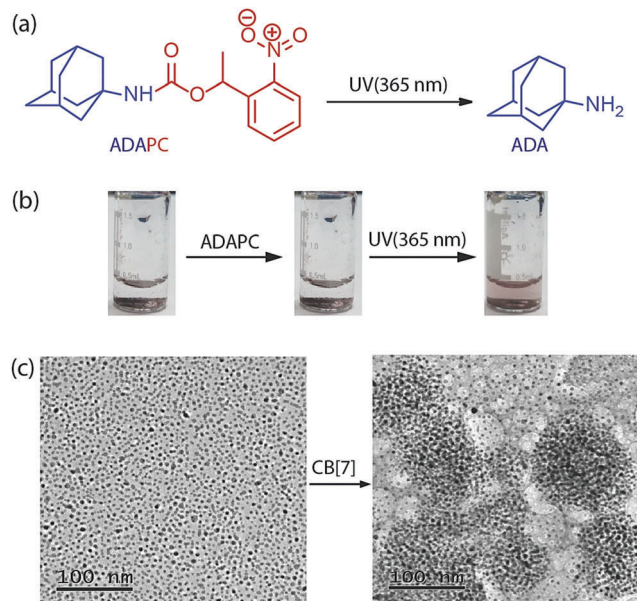


Fig. 2 (a) Photocleavage of ADAPC to ADA. (b) Images of light triggered disassembly of an NP-CB[7] complex. An assembly treated with ADAPC does not disperse but irradiation with UV light disassembled the assembly and generates dispersed nanoparticles. (c) TEM images of 5 nm AuNPs in a dispersed state (left) and an aggregated state (right).



Finally, we checked the ADA triggered activation *via* cell culture studies. For this study, the Saphenous Vein Endothelial Cell line (SVEC) was treated with the DOX loaded AuNP assembly and triggered with ADA. Additionally, two control experiments were performed to provide support for ADA triggered activation. In one case, we employed the DOX loaded AuNP assembly but performed cell culture studies without the ADA trigger. In another case, we used the AuNP assembly and added the ADA trigger to determine toxicity from the delivery vector. After treating the cells with the control and triggered set, cellular morphology was investigated by acquiring bright field images and Calcein AM staining (Fig. 5a). An Alamar Blue cell

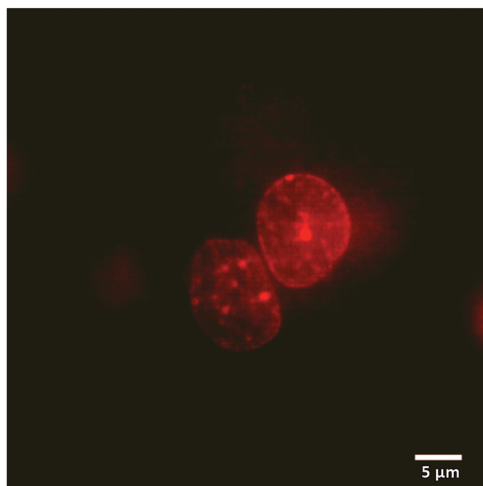


Fig. 4 Fluorescence image of the nucleus of HeLa cells treated with NP + DOX + CB[7] and triggered with ADA for 6 h. Assembly encapsulated DOX was released after the triggered action of ADA and enters into the cellular nucleus.

viability test was performed to quantitatively assay the cytotoxicity from the different control and triggered sets (Fig. 5b). A significantly increased cell death was observed in the case of the ADA triggered DOX loaded AuNP assembly as compared to the DOX loaded AuNP assembly itself, indicating enhanced drug release upon triggered activation. We also observed that the amount of cell death could be controlled by the amount of given trigger (*i.e.* ADA), indicating the ability to control the drug

dosing *via* the given trigger amount (Fig. S19 and S20, ESI†). Additionally, we did not observe any cytotoxicity when cells were treated with only assembly (without DOX) and triggered with ADA, indicating negligible toxicity either from AuNP assemblies or from the ADA trigger (Fig. 5). Overall these results establish that the supramolecular assemblies provide a non-toxic platform that effectively controls the payload release upon exposure to a high-affinity competitive guest.

Conclusions

In conclusion, we demonstrated a new strategy for controlling drug release rate through the use of competitive interactions of orthogonally presented guest molecules. Triggered release by small chemical stimuli is an important advancement as they could be externally regulated while having the abilities to reach and activate delivery systems in deep tissue. Our system has the capability of easy encapsulation of drug molecules as well as various macromolecular therapeutic molecules in its active and functional state without any chemical modification. Due to ease of fabrication and versatility, we envision that dynamic host-guest nanoparticle assembly directed by a small molecule trigger will play an important role in further developing stimuli responsive drug delivery systems. In addition, we expect that delivery based on reversible supramolecular interaction will pave the way for developing a new strategy for the refilling of implantable drug depots.³⁵ Translating this system for *in vivo* delivery is planned and will be reported in due course.



Fig. 5 Comparison of cytotoxicity possessed by release of DOX from the AuNP assembly. SVECs were treated with a variety of conditions, including NP + CB[7] + ADA, NP + DOX + CB[7] and NP + DOX + CB[7] + ADA. (a) Bright field image of the cells and the corresponding Calcein AM stained image. (b) Alamar Blue cell viability assay showing the cytotoxicity effect under various conditions. The studies were performed in triplicate and the error bars represent standard error of the mean. $**p \leq 0.01$. Scale bar 50 μm .



Conflicts of interest

No conflict of interest.

Acknowledgements

This work was supported by a Wellcome Trust-DBT India Alliance Intermediate Fellowship (IA/I/16/1/502368), a DBT Innovative Young Biotechnologist Award (IYBA) (BT/09/IYBA/2015/15), an SERB Early Career Research Award (ECR/2016/002052), a DAE-BRNS Young Scientist's Research Award (YSRA) (37(1)/20/01/2017-BRNS), and a JNCASR Startup Fund to S. S. A. and R. S. acknowledges support from CSIR for a Graduate Research Fellowship.

Notes and references

- 1 K. Park, *J. Controlled Release*, 2014, **190**, 3–8.
- 2 Y. H. Yun, B. K. Lee and K. Park, *J. Controlled Release*, 2015, **219**, 2–7.
- 3 C. J. Kearney and D. J. Mooney, *Nat. Mater.*, 2013, **12**, 1004.
- 4 R. Liu, W. Xiao, C. Hu, R. Xie and H. Gao, *J. Controlled Release*, 2018, **278**, 127–139.
- 5 Y. Brudno and D. J. Mooney, *J. Controlled Release*, 2015, **219**, 8–17.
- 6 S. S. Agasti, A. Chompoosor, C.-C. You, P. Ghosh, C. K. Kim and V. M. Rotello, *J. Am. Chem. Soc.*, 2009, **131**, 5728–5729.
- 7 K. Kim, M.-C. Jo, S. Jeong, L. Palanikumar, V. M. Rotello, J.-H. Ryu and M.-H. Park, *Nanoscale*, 2016, **8**, 11949–11955.
- 8 S. Ruan, M. Yuan, L. Zhang, G. Hu, J. Chen, X. Cun, Q. Zhang, Y. Yang, Q. He and H. Gao, *Biomaterials*, 2015, **37**, 425–435.
- 9 S. Mura, J. Nicolas and P. Couvreur, *Nat. Mater.*, 2013, **12**, 991.
- 10 H. Chen, D. Liu and Z. Guo, *Chem. Lett.*, 2016, **45**, 242–249.
- 11 A. P. Blum, J. K. Kammeyer, A. M. Rush, C. E. Callmann, M. E. Hahn and N. C. Gianneschi, *J. Am. Chem. Soc.*, 2015, **137**, 2140–2154.
- 12 M. Karimi, P. Sahandi Zangabad, S. Baghaee-Ravari, M. Ghazadeh, H. Mirshekari and M. R. Hamblin, *J. Am. Chem. Soc.*, 2017, **139**, 4584–4610.
- 13 J. Li and P. R. Chen, *Nat. Chem. Biol.*, 2016, **12**, 129.
- 14 J.-M. Lehn, *Chem. Soc. Rev.*, 2007, **36**, 151–160.
- 15 X. Ma and Y. Zhao, *Chem. Rev.*, 2015, **115**, 7794–7839.
- 16 J. Murray, K. Kim, T. Ogoshi, W. Yao and B. C. Gibb, *Chem. Soc. Rev.*, 2017, **46**, 2479–2496.
- 17 B. V. K. J. Schmidt and C. Barner-Kowollik, *Angew. Chem., Int. Ed.*, 2017, **56**, 8350–8369.
- 18 S. J. Barrow, S. Kasera, M. J. Rowland, J. del Barrio and O. A. Scherman, *Chem. Rev.*, 2015, **115**, 12320–12406.
- 19 F. Biedermann, U. Rauwald, J. M. Zayed and O. A. Scherman, *Chem. Sci.*, 2011, **2**, 279–286.
- 20 D. Debapratim and O. A. Scherman, *Isr. J. Chem.*, 2011, **51**, 537–550.
- 21 S. Ghosh and L. Isaacs, *J. Am. Chem. Soc.*, 2010, **132**, 4445–4454.
- 22 C. Kim, S. S. Agasti, Z. Zhu, L. Isaacs and V. M. Rotello, *Nat. Chem.*, 2010, **2**, 962.
- 23 G. Y. Tonga, Y. Jeong, B. Duncan, T. Mizuhara, R. Mout, R. Das, S. T. Kim, Y.-C. Yeh, B. Yan, S. Hou and V. M. Rotello, *Nat. Chem.*, 2015, **7**, 597.
- 24 C. Kim, G. Y. Tonga, B. Yan, C. S. Kim, S. T. Kim, M.-H. Park, Z. Zhu, B. Duncan, B. Creran and V. M. Rotello, *Org. Biomol. Chem.*, 2015, **13**, 2474–2479.
- 25 K. I. Assaf and W. M. Nau, *Chem. Soc. Rev.*, 2015, **44**, 394–418.
- 26 R. Oun, R. S. Floriano, L. Isaacs, E. G. Rowan and N. J. Wheate, *Toxicol. Res.*, 2014, **3**, 447–455.
- 27 P. Neiryneck, J. Brinkmann, Q. An, D. W. J. van der Schaft, L.-G. Milroy, P. Jonkheijm and L. Brunsveld, *Chem. Commun.*, 2013, **49**, 3679–3681.
- 28 D.-W. Lee, K. M. Park, M. Banerjee, S. H. Ha, T. Lee, K. Suh, S. Paul, H. Jung, J. Kim, N. Selvapalam, S. H. Ryu and K. Kim, *Nat. Chem.*, 2010, **3**, 154.
- 29 A. Youngjoo, J. Yoonjung, S. Narayanan, Y. Gyeongwon and K. Kimoon, *Angew. Chem., Int. Ed.*, 2013, **52**, 3140–3144.
- 30 C. Liping, H. Gaya, B. Volker and I. Lyle, *Angew. Chem., Int. Ed.*, 2013, **52**, 12033–12037.
- 31 N. D. B. Le, G. Yesilbag Tonga, R. Mout, S.-T. Kim, M. E. Wille, S. Rana, K. A. Dunphy, D. J. Jerry, M. Yazdani, R. Ramanathan, C. M. Rotello and V. M. Rotello, *J. Am. Chem. Soc.*, 2017, **139**, 8008–8012.
- 32 L. H. Hee, C. T. Su, S. J. C. Lee, L. J. Wha, P. Junghong, K. Y. Ho, K. W. Jong, K. Kimoon and H. I. Kim, *Angew. Chem., Int. Ed.*, 2014, **53**, 7461–7465.
- 33 H. Ilha, J. W. Sung, K. Hee-Joon, K. Dongwoo, K. Hyunuk, S. Narayanan, F. Norifumi, S. Seiji and K. Kim, *Angew. Chem., Int. Ed.*, 2007, **46**, 210–213.
- 34 G. Yesilbag Tonga, T. Mizuhara, K. Saha, Z. Jiang, S. Hou, R. Das and V. M. Rotello, *Tetrahedron Lett.*, 2015, **56**, 3653–3657.
- 35 Y. Brudno, E. A. Silva, C. J. Kearney, S. A. Lewin, A. Miller, K. D. Martinick, M. Aizenberg and D. J. Mooney, *Proc. Natl. Acad. Sci. U. S. A.*, 2014, **111**, 12722–12727.

