

Cite this: *Nanoscale Adv.*, 2019, 1, 1387

2D-MoS₂ nanosheets as effective hole transport materials for colloidal PbS quantum dot solar cells†

Srikanth Reddy Tulsani,^{ab} Arup K. Rath^{ab} and Dattatray J. Late^{*ab}

Herein, we demonstrate for the first time matrix-free deposition of two dimensional (2D) MoS₂ nanosheets as an efficient hole transport layer (HTL) for colloidal lead sulfide (PbS) quantum dot (QD) solar cells. We have developed all-solution-processed n-p-p⁺ architecture solar cells where ZnO nanoparticles were used as an n-type window layer, a PbS QD layer acted as a light absorbing p-type layer and 2D-MoS₂ nanosheets acted as a p⁺-type hole transport layer. The MoS₂ nanosheets allow better interface with the PbS QD layers. The incorporation of the MoS₂ hole transport layer leads to superior fill factor, higher open circuit voltage and better performance in colloidal PbS QD solar cells. These results show that one layer of MoS₂ nanosheets improves the power conversion efficiency of the device from 0.92% for a hole transport material free device to 2.48%. The present work reveals the development of 2D-MoS₂ nanosheets as a new hole transport layer for the fabrication of cost-effective, durable and efficient colloidal PbS quantum dot solar cells.

Received 5th October 2018
Accepted 1st January 2019

DOI: 10.1039/c8na00272j

rsc.li/nanoscale-advances

1 Introduction

In recent years two-dimensional (2D) transition metal dichalcogenides (TMDs) have attracted widespread attention because of their potential application in optoelectronic devices,¹ catalysis,² transistors,^{3–5} photonics,^{6–9} photodetectors,¹⁰ electronics,¹¹ sensors,^{12,13} memories,^{14,15} and photocatalyzed hydrogen evolution reactions.^{16–18} Among all TMDs, 2D MoS₂ attracted significant interest due to its unique graphene like properties along with remarkable optoelectronic properties, like variable energy band gap, high conductivity, good flexibility, high transparency, high surface area, *etc.* In comparison to monolayer graphene,¹⁹ which is semi-metallic, monolayer MoS₂ shows semiconducting characteristics with a direct band gap. Furthermore, the thickness dependent band gap changing from an indirect band gap in bulk to a direct bandgap in monolayer MoS₂ has opened up several applications.²⁰

The development of 2D TMD-based solar cell devices is, however, limited due to the difficulties in fabricating large-scale defect-free 2D TMD materials. Even though the nanosheets, nanoparticles and bulk forms of TMD materials have been used in solar cell devices,^{21–23} they have not yet been explored in colloidal quantum dot based solar cells. For example, Shanmugan *et al.* have fabricated 220 nm thick MoS₂ nano-membranes stacked with Au and achieved a solar cell

efficiency of 1.8% by making a Schottky junction at the MoS₂/Au interface.²¹ The bulk hetero-junction MoS₂/TiO₂ nanocomposite material was used in solar cells, which showed a power conversion efficiency of 1.3%.²² Further, MoS₂/graphene and WS₂/MoS₂ based atomically thin solar cell devices have been reported with exceptionally large power densities per kilogram (450–1800 kW kg^{−1}).^{24,25} However, due to the high transmission loss in these monolayer-based devices, the efficiencies of WS₂/MoS₂ and MoS₂/graphene based solar cells remained below 2%.

For the commercial viability of solar cell devices, it is of great importance to develop materials with ease of synthesis, cost-effective device building and high throughput performance. This can be achieved by either further improvement in the solar cell efficiency^{26,27} or reducing the cost^{28,29} of the devices or both. Silicon based solar cells have dominated the photovoltaic industry due to their abundance, high performance and mature processing technology.²⁶ Therefore, in addition to exploring 2D materials, it will be of great interest to investigate their capability for solar energy conversion applications. To reach the goal, wafer-scale fabrication methods for 2D materials have recently been implemented.^{30–32} To date, devices based on large-area multilayer TMD materials have not yet been widely established due to the stringent growth conditions of 2D TMD materials.

Here for the first time, we report MoS₂ nanosheets as a hole transport material for colloidal PbS quantum dot solar cells. The surface of the MoS₂ nanosheets is functionalized with molecular iodine to disperse them in DMF. This allows the matrix free deposition of MoS₂ on top of the PbS QD layer for hole transport layer formation. The valence band position of the

^aPhysical and Materials Chemistry Division, CSIR-National Chemical Laboratory, Dr Homi Bhabha Road, Pune, 411008, India. E-mail: dj.late@nccl.res.in; datta099@gmail.com

^bAcademy of Scientific and Innovative Research (AcSIR), Ghaziabad-201002, India

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8na00272j

MoS₂ layer matches well with that of PbS QDs for efficient hole transfer, which has been exploited to improve the photovoltaic performance of solar cell devices.

2 Experimental section

Chemicals used

Sodium molybdate dihydrate (>99.0%), sulfur powder, sodium borohydride (>98.0%), *N,N*-dimethylformamide (99.8%), tetrabutylammonium iodide (TBAI) (98.0%), lead oxide (99.0%), 1-octadecene (90%), oleic acid (90%), bis(trimethylsilyl) sulfide (TMS), zinc acetate trihydrate (99.8%), 2-methoxyethanol (99.9%), ethanolamine (99%), 1,2-ethanedithiol (>98.0%) (EDT), acetone, methanol and toluene were purchased from Sigma-Aldrich. Solvents used in reactions are all anhydrous. The DI water used had a resistivity of 18.2 million ohm cm.

Synthesis of MoS₂ nanosheets

The MoS₂ nanosheets were synthesized by using a facile hydrothermal route.³³ Briefly, in this synthesis process, 0.56 grams of Na₂MoO₄, 0.25 grams of sulphur powder and 0.1 gram of NaBH₄ were weighed, dissolved in 40 mL of DI water and stirred for half an hour to achieve proper dispersion in DI water. Then the reaction mixture was transferred into a Teflon lined stainless steel autoclave and kept at 200 °C for 24 hours. After cooling down to room temperature, the product was cleaned

with DI water twice, followed by washing with ethanol twice, and then it was centrifuged at 5500 rpm. Finally, the product was dried in a vacuum oven to remove the residual solvents from the material. The as-synthesized MoS₂ material was taken in 3 mL DMF solvent. 200 mg TBAI was added to the solution and the mixture was heated at 100 °C under continuous stirring for 12 hours under an Ar atmosphere. Iodine functionalized MoS₂ nanosheets were then isolated by addition of toluene, followed by centrifugation. The dry MoS₂ powder was then dispersed in DMF at a concentration of 20 mg mL⁻¹ for film fabrication.

PbS QD synthesis

The PbS QDs were synthesized by using the hot injection method.³⁴ Briefly, 0.45 grams of lead oxide, 3 mL octadecene (degassed under vacuum for 12 hours before using) and 1.5 mL oleic acid were mixed in a three neck round bottom (RB) flask and kept in a vacuum at 95 °C using a standard Schlenk line for 12 hours. The reaction mixture turned into a clear solution upon the formation of the lead oleate complex. The reaction with vacuum (10⁻² mbar) environment was then purged with argon gas. Then 15 mL octadecene was added to this reaction mixture and the temperature was set to 120 °C. At this temperature, 210 μL TMS dissolved in 10 mL octadecene was then injected quickly into the reaction bath without delay and

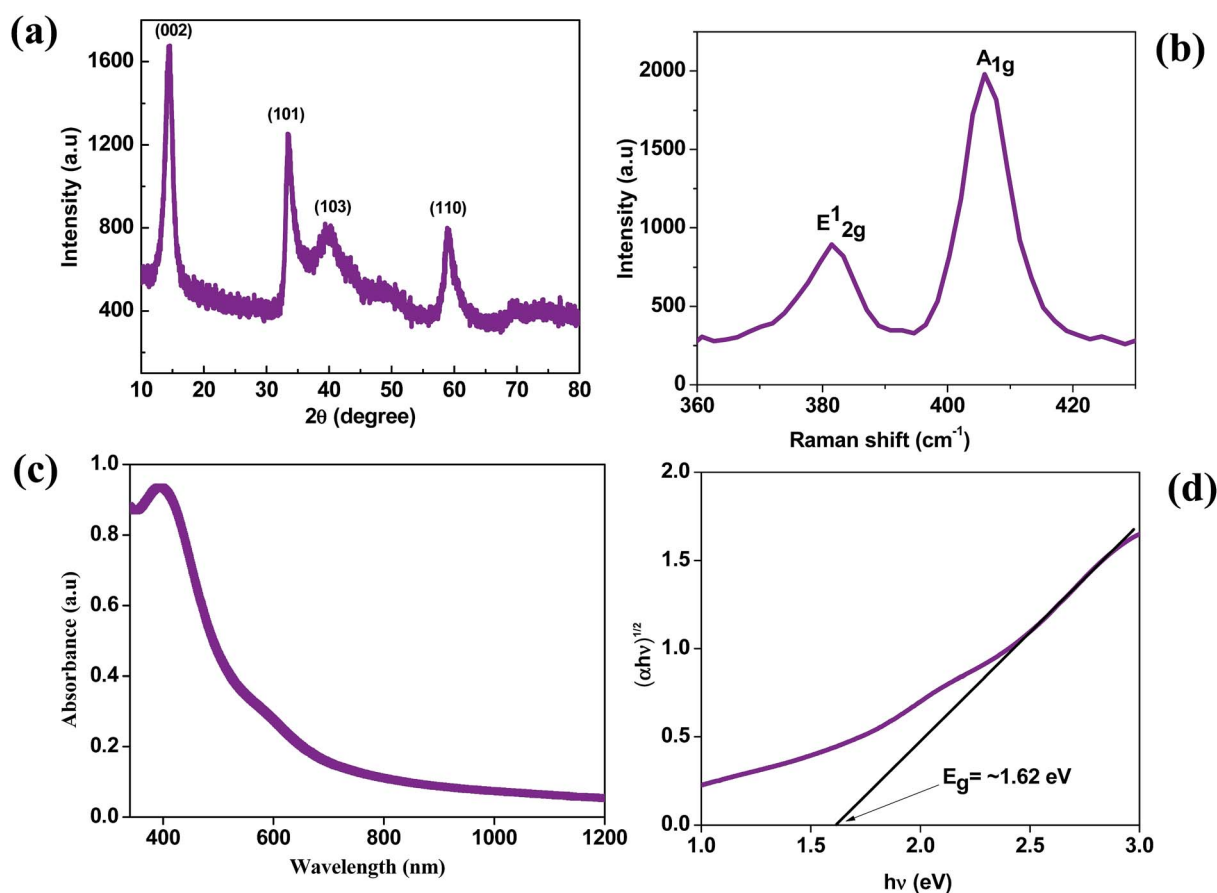


Fig. 1 (a) X-ray diffraction pattern of MoS₂. (b) Raman spectrum of MoS₂. (c) Absorption spectrum and (d) Tauc plot of MoS₂.



the entire solution turned dark brown immediately, indicating PbS nucleation. The heating source was switched off and the reaction bath was allowed to cool down naturally to room temperature. After reaching room temperature, 24 mL of acetone was then added to the reaction bath and the mixture was allowed to stir for 3 minutes. The PbS QDs were isolated by centrifugation at 3500 rpm for 5 minutes. To clean the QDs they were dispersed in a small amount (~ 3 mL) of toluene, precipitated with 24 mL of acetone, followed by centrifugation, and finally dispersed in toluene.

ZnO sol-gel synthesis

The zinc oxide sol-gel solution was prepared by dissolving 1 gram of zinc acetate, 10 mL 2-methoxyethanol and 284 microliters of ethanolamine added in the same sequence at room temperature.³⁵ The precursor solution was continuously stirred overnight at room temperature to induce hydrolysis in the presence of air. The solution was filtered through a $0.2\ \mu\text{m}$ syringe filter for further use in device fabrication.

ZnO film deposition

Commercially available indium tin oxide (ITO) coated glass substrates were first etched by using hydrochloric acid and zinc

dust. After etching, they were sonicated in a soap solution, DI water, acetone and isopropanol for 30 minutes each and finally the substrates were cleaned in boiling isopropanol for 15 minutes. Then the ZnO sol-gel filtered solution was spin coated on the ITO substrates at a rotation speed of 3500 rpm for 30 s. The as-deposited films were then annealed at $200\ ^\circ\text{C}$ for 10 minutes. The substrates were then coated with another layer of ZnO under the same spinning conditions and annealed at $260\ ^\circ\text{C}$ for 30 minutes.

Solar cell device fabrication

As prepared above ZnO substrates were then used for PbS QD deposition. PbS QDs were deposited *via* a layer by layer (LBL) solid state ligand exchange approach under ambient conditions.³⁶ 1,2-Ethanedithiol (EDT) 2% v/v in acetonitrile solution was used as a ligand for the deposition of PbS QDs. The film deposition steps followed in this work were as follows: PbS QDs ($30\ \text{mg mL}^{-1}$ in toluene) were first spin coated at 2500 rpm on the substrates for 30 seconds. Under continuous spinning 4 drops of EDT were added, followed by rinsing with 8 drops of acetonitrile to remove excess EDT. This completes one layer of PbS QD film deposition. The sequence was repeated to grow layer by layer films up to 8 layers. On top of the PbS QD films, one layer of MoS_2 ($20\ \text{mg mL}^{-1}$) was deposited by spin coating at

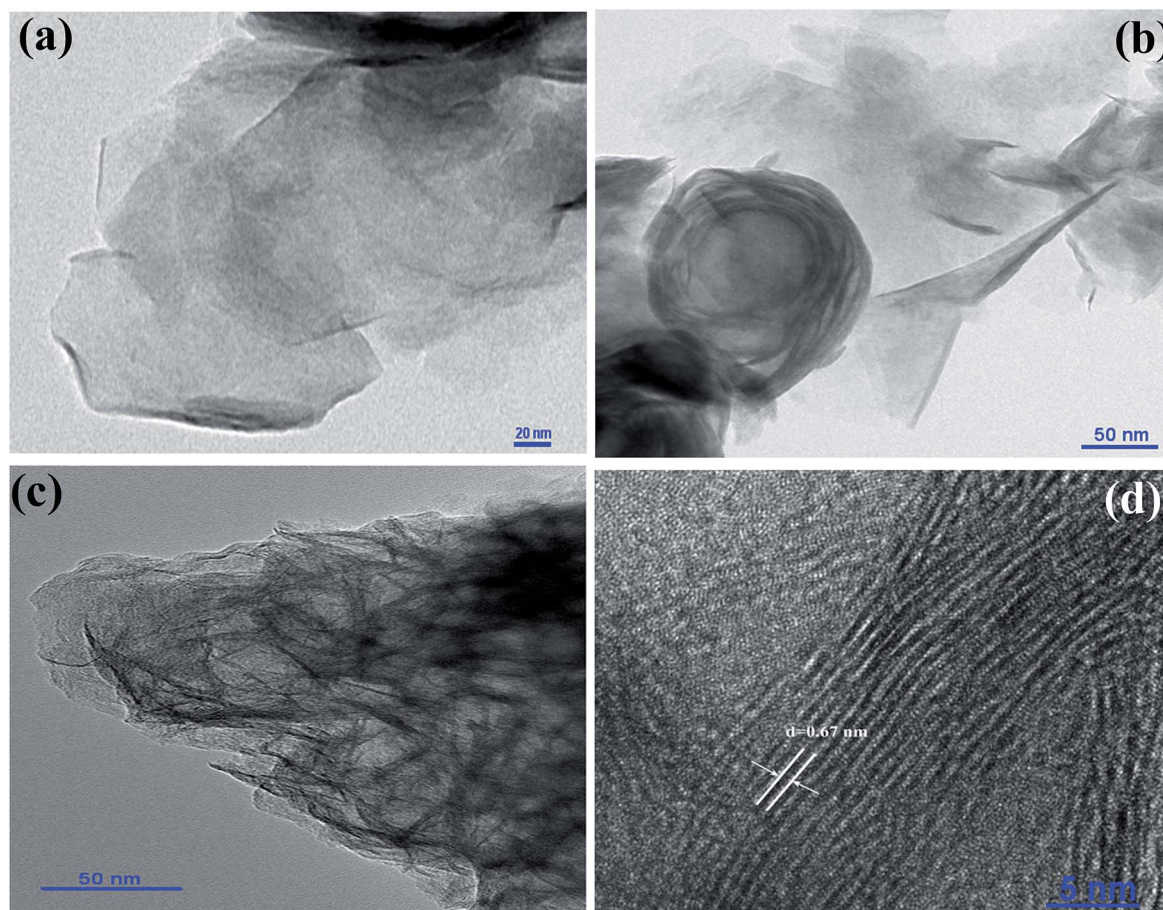


Fig. 2 (a)–(d) show the TEM images of MoS_2 . *d*-Spacing between the MoS_2 layers shown in figure (d) is 0.67 nm.



the c -axis and the in-plane E_{2g}^1 mode indicates the opposite vibration of two S atoms relative to the Mo atom. The Raman frequencies of A_{1g} and E_{2g}^1 peaks change with the number of layers in the MoS_2 nanosheets, and the frequency difference between A_{1g} and E_{2g}^1 modes is 24.5 cm^{-1} which corresponds to the multilayer nature of the as-synthesized MoS_2 nanosheets.³⁸

To estimate the band gap of the as-synthesized MoS₂ nanosheets, we measured the absorption spectra as shown in Fig. 1(c). The small noticeable peak at ~600 nm corresponds to the spin-orbit split pair originating from the band edge excitonic transitions at the *K* point of the Brillouin zone.³⁹ The broad peak at ~395 nm corresponds to interband transitions from the occupied d_{x²-y²} orbital to unoccupied d_{xy}, d_{yz}, d_{xz} and d_{x²-y²} orbitals.⁴⁰ From the absorption spectra, the calculated optical band gap is found to be ~1.62 eV by using the Tauc plot with the allowed transitions for the MoS₂ nanosheets.

Fig. S1 (a and b)† shows the typical scanning electron microscopy (SEM) images of the MoS₂, indicating the nanosheet morphology of the as-synthesized material of few micrometers in length. High-resolution transmission electron microscopy (HR-TEM) was used for further analysis of MoS₂ nanosheets. Fig. 2 (a-d) show the high-resolution TEM images of MoS₂ nanosheets; all the TEM images suggest a nanosheet-like morphology, consistent with SEM images. The folded edges show parallel lines in Fig. 2(d), corresponding to different layers of MoS₂ sheets with a *d*-spacing of ~ 0.67 nm. The corresponding selected area electron diffraction (SAED) patterns

Fig. 3 (a) AFM image of MoS₂ nanosheets and (b) corresponding AFM height profile of MoS₂ nanosheets.

This journal is © The Royal Society of Chemistry 2019

shown in Fig. S2[†] indicate the crystalline nature of MoS₂ nanosheets which supports the XRD and high-resolution TEM results. Further, energy dispersive X-ray analysis (EDAX) of MoS₂ nanosheets was carried out. EDAX data are shown in ESI Fig. S3,[†] showing the stoichiometric ratios between Mo and S. Absorption spectra of oleic acid capped PbS quantum dots dispersed in toluene are shown in ESI Fig. S4.[†] The TEM images of PbS quantum dots are shown in Fig. S5,[†] indicating mono-dispersed QDs with an average size of ~ 3.2 nm.

Fig. 3(a) shows the contact mode atomic force microscopy (AFM) topography of a thin MoS₂ nanosheet deposited on a Si substrate. We have used contact mode AFM to determine the thickness and to characterize the topography of the deposited sheets. The height profile obtained from the solid white line is shown in Fig. 3(b). It is noted that the height of the MoS₂ nanosheet deposited on a Si substrate is found to be ~ 10 nm. The as-synthesized MoS₂ nanosheets are used as a hole transport layer to build PbS quantum dot solar cells. The solar cell device architecture is shown in Fig. 4(a) and the corresponding cross sectional SEM image is shown in Fig. 4(b). The typical I - V characteristics for devices with and without the MoS₂ hole transport layer are shown in Fig. 4(c). The device without MoS₂ shows a power conversion efficiency of 0.92%, with an open

circuit voltage (V_{oc}) of 0.46 V, a short circuit current density (J_{sc}) of 6.84 mA cm^{-2} and a fill factor of 30%. The insertion of MoS₂ nanosheets as a hole transport layer improves the efficiency from 0.92% to 2.48% due to overall increments in V_{oc} , J_{sc} and FF. The EQE results shown in Fig. 4(d) show higher photon to current conversion ratios for the entire wavelength range for the device with MoS₂ nanosheets compared with the pristine device. The increase in EQE (%) and J_{sc} is attributed to superior charge collection in the latter case. The photovoltaic figures of merits of the photovoltaic devices are shown in Table 1. Fig. 5(a) shows the typical statistical variations in the efficiency of five solar cell devices. The enhancement in photovoltaic performance due to the insertion of the MoS₂ layer is explained by the energy band diagram, shown in Fig. 5(b). In the absence of the MoS₂ layer photo generated electrons and holes both are

Table 1 Device performance of solar cells with and without molybdenum disulfide

Device	V_{oc} (V)	J_{sc} (mA cm^{-2})	Fill factor	Efficiency ($\eta\%$)
Without MoS ₂	0.46	6.84	0.30	0.92
With MoS ₂	0.60	9.30	0.45	2.48

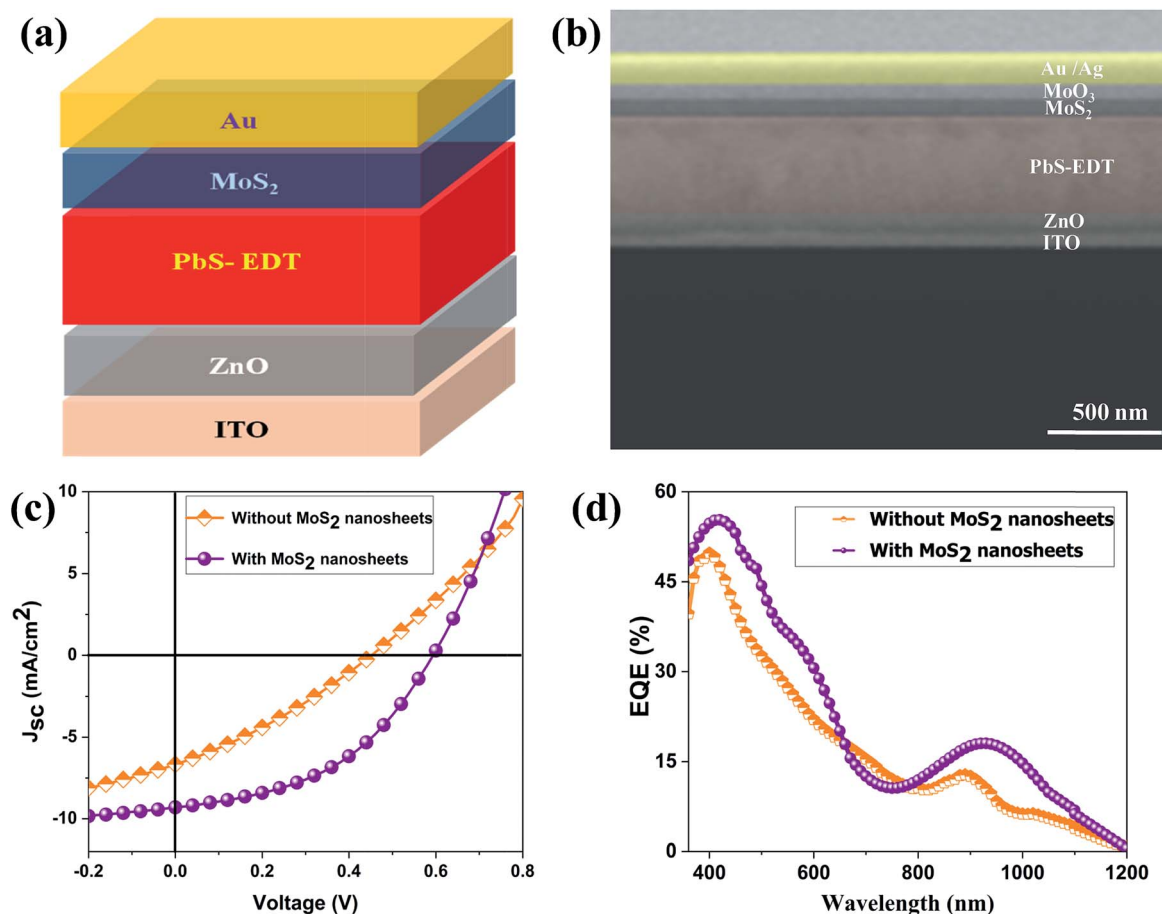


Fig. 4 (a) Solar cell device architecture. (b) Cross sectional SEM image of the device. (c) The I - V characteristics of the solar cells. (d) External quantum efficiency (EQE) of the solar cells.



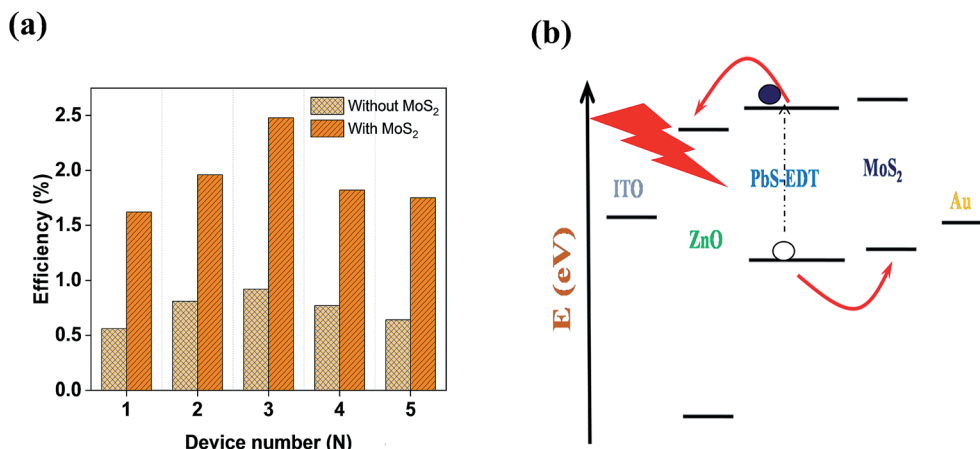


Fig. 5 (a) Statistical variation of the solar cells. (b) Energy level diagram of a solar cell.

allowed to transfer to the Au electrode. This would enhance the photo carrier recombination at the PbS–Au interface and thereby reduce the current generation of the solar cells. Further, the 1.62 eV band gap of the MoS₂ layer pushes its conduction band position well above the conduction band of PbS QDs, which blocks the transfer of electrons from PbS to the MoS₂ layer. The selective extraction of holes at the PbS–MoS₂ interface reduces the recombination of the photo generated carriers, thereby enhancing the current generation of the solar cells. Further, the hole carrier selectivity of the MoS₂ layer reduces the voltage loss by reducing the Fermi energy pinning at the PbS–Au interface which helps to increase the voltage generation and fill factor of the solar cells.

4 Conclusions

In conclusion, we have demonstrated the matrix free deposition of 2D MoS₂ nanosheets by the spin coating process. We have successfully developed a hole transport layer by using 2D MoS₂ nanosheets, which improves the efficiency of PbS quantum dot solar cell devices from ~0.92% to ~2.48%. In solar cell devices it improves the charge extraction and reduces the carrier recombination. These improvements help to boost the efficiency of the solar cells by enhancing the short circuit current, open circuit voltage and fill factor. Our results open up new opportunities to use inorganic 2D MoS₂ as an alternative to organic hole transporting materials for the development of the next generation solar cell devices.

Conflicts of interest

All authors declare no conflicts of interest.

Acknowledgements

We would like to thank the funding agencies SERB extramural funding, India (No: EMR/2015/002415), DST Nanomission, India (No: SR/NM/NT-1011/2105 (G)), and UGC SRF fellowship

no. 2121251076. Dr D. J. Late would like to thank SERB for the SERB Research scientist grant.

References

- 1 I. B. Amara, E. B. Salem and S. Jaziri, Optoelectronic response and excitonic properties of monolayer MoS₂, *J. Appl. Phys.*, 2016, **120**, 051707.
- 2 Q. Xiang, J. Yu and M. Jaroniec, Synergetic Effect of MoS₂ and Graphene as Cocatalysts for Enhanced Photocatalytic H₂ Production Activity of TiO₂ Nanoparticles, *J. Am. Chem. Soc.*, 2012, **134**, 6575–6578.
- 3 D. J. Late, B. Liu, H. S. S. R. Matte, V. P. Dravid and C. N. R. Rao, Hysteresis in Single-Layer MoS₂ Field Effect Transistors, *ACS Nano*, 2012, **6**, 5635–5641.
- 4 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, Single-Layer MoS₂ Transistors, *Nat. Nanotechnol.*, 2011, **6**, 147–150.
- 5 F. A. McGuire, Y. C. Lin, K. Price, G. B. Rayner, S. Khandelwal, S. Salahuddin and A. D. Franklin, Sustained Sub-60 mV/decade Switching via the Negative Capacitance Effect in MoS₂ Transistors, *Nano Lett.*, 2017, **17**, 4801–4806.
- 6 W. Zhang, J. K. Huang, C. H. Chen, Y. H. Chang, Y. J. Cheng and L. J. Li, High-Gain Photo-transistors Based on a CVD MoS₂ Monolayer, *Adv. Mater.*, 2013, **25**, 3456–3461.
- 7 D. S. Tsai, K. K. Liu, D. H. Lien, M. L. Tsai, C. F. Kang, C. A. Lin, L. J. Li and J. H. He, Few-Layer MoS₂ with High Broadband Photogain and Fast Optical Switching for Use in Harsh Environments, *ACS Nano*, 2013, **7**, 3905–3911.
- 8 K. P. Wang, Y. Y. Feng, C. X. Chang, J. X. Zhan, C. W. Wang, Q. Z. Zhao, J. N. Coleman, L. Zhang, W. J. Blau and J. Wang, Broadband Ultrafast Nonlinear Absorption and Nonlinear Refraction of Layered Molybdenum Dichalcogenide Semiconductors, *Nanoscale*, 2014, **6**, 10530–10535.
- 9 K. P. Wang, J. Wang, J. T. Fan, M. Lotya, A. O'Neill, D. Fox, Y. Y. Feng, X. Y. Zhang, B. X. Jiang, Q. Z. Zhao, H. Z. Zhang, J. N. Coleman, L. Zhang and W. J. Blau, Ultrafast Saturable Absorption of Two-Dimensional MoS₂ Nanosheets, *ACS Nano*, 2013, **7**, 9260–9267.



- 10 W. Zhang, C. P. Chu, J. K. Huang, C. H. Chen, M. L. Tsai, Y. H. Chang, C. T. Liang, Y. Z. Chen, Y. L. Chueh and J. H. He, Ultrahigh-Gain Photodetectors Based on Atomically Thin Graphene MoS₂ Heterostructures, *Sci. Rep.*, 2014, **4**, 3826.
- 11 Q. H. Wang, K. K. Zadeh, A. Kis, J. N. Coleman and M. S. Strano, Electronics and Optoelectronics of Two-Dimensional Transition Metal Dichalcogenides, *Nat. Nanotechnol.*, 2012, **7**, 699–712.
- 12 J. Zhao, N. Li, H. Yu, Z. Wei, M. Liao, P. Chen, S. Wang, D. Shi, Q. Sun and G. Zhang, Highly Sensitive MoS₂ Humidity Sensors Array for Noncontact Sensation, *Adv. Mater.*, 2017, **29**, 1702076.
- 13 D. J. Late, Y. K. Huang, B. Liu, J. Acharya, S. N. Shirodkar, J. Luo, A. Yan, D. Charles, U. V. Waghmare, V. P. Dravid and C. N. R. Rao, Sensing Behavior of Atomically Thin-Layered MoS₂ Transistors, *ACS Nano*, 2013, **7**, 4879–4891.
- 14 S. Bertolazzi, D. Krasnozhan and A. Kis, Nonvolatile, Memory Cells Based on MoS₂/Graphene Heterostructures, *ACS Nano*, 2013, **7**, 3246–3252.
- 15 K. Roy, M. Padmanabhan, S. Goswami, T. P. Sai, G. Ramalingam, S. Raghavan and A. Ghosh, Graphene–MoS₂ hybrid structures for multifunctional photoresponsive memory devices, *Nat. Nanotechnol.*, 2013, **8**, 826–830.
- 16 Y. Hou, A. B. Laursen, J. Zhang, G. Zhang, Y. Zhu, X. Wang, S. Dahl and I. Chorkendorff, Layered Nanojunctions for Hydrogen-Evolution Catalysis, *Angew. Chem., Int. Ed.*, 2013, **52**, 3621–3625.
- 17 H. Wang, Z. Lu, D. Kong, J. Sun, T. M. Hymel and Y. Cui, Electrochemical Tuning of MoS₂ Nanoparticles on Three Dimensional Substrate for Efficient Hydrogen Evolution, *ACS Nano*, 2014, **8**, 4940–4947.
- 18 Z. Wang and B. Mi, Environmental Applications of 2D Molybdenum Disulfide (MoS₂) Nanosheets, *Environ. Sci. Technol.*, 2017, **51**, 8229–8244.
- 19 K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, Electric Field Effect in Atomically Thin Carbon Films, *Science*, 2004, **306**, 666–669.
- 20 R. Ganatra and Q. Zhang, Few-Layer MoS₂: A Promising Layered Semiconductor, *ACS Nano*, 2014, **8**, 4074–4099.
- 21 M. Shanmugam, C. A. Durcan and B. Yu, Layered Semiconductor Molybdenum Disulfide Nanomembrane Based Schottky-Barrier Solar Cells, *Nanoscale*, 2012, **4**, 7399–7405.
- 22 M. Shanmugam, T. Bansal, C. A. Durcan and B. Yu, Molybdenum Disulphide/Titanium Dioxide Nanocomposite-Poly 3-hexylthiophene Bulk Heterojunction Solar Cell, *Appl. Phys. Lett.*, 2012, **100**, 153901.
- 23 X. Gu, W. Cui, H. Li, Z. Wu, Z. Zeng, S. T. Lee, H. Zhang and B. Sun, A Solution-Processed Hole Extraction Layer Made from Ultrathin MoS₂ Nanosheets for Efficient Organic Solar Cells, *Adv. Energy Mater.*, 2013, **3**, 1262–1268.
- 24 M. Bernardi, M. Palummo and J. C. Grossman, Extraordinary Sunlight Absorption and One Nanometer Thick Photovoltaics Using Two-Dimensional Monolayer Materials, *Nano Lett.*, 2013, **13**, 3664–3670.
- 25 L. Y. Gan, Q. Zhang, Y. Cheng and U. Schwingenschlögl, Photovoltaic Heterojunctions of Fullerenes with MoS₂ and WS₂ Monolayers, *J. Phys. Chem. Lett.*, 2014, **5**, 1445–1449.
- 26 H. P. Wang, T. Y. Lin, C. W. Hsu, M. L. Tsai, C. H. Huang, W. R. Wei, M. Y. Huang, Y. J. Chien, P. C. Yang and C. W. Liu, Realizing High-Efficiency Omni directional n-Type Si Solar Cells via the Hierarchical Architecture Concept with Radial Junctions, *ACS Nano*, 2013, **7**, 9325–9335.
- 27 H. P. Wang, T. Y. Lin, M. L. Tsai, W. C. Tu, M. Y. Huang, P. C. Yang, Y. J. Chien, C. W. Liu, Y. L. Chueh and J. H. He, Toward Efficient and Omnidirectional n-Type Si Solar Cells: Concurrent Improvement in Optical and Electrical Characteristics by Employing Microscale Hierarchical Structures, *ACS Nano*, 2014, **3**, 2959–2969.
- 28 S. H. Tsai, H. C. Chang, H. H. Wang, S. Y. Chen, C. A. Lin, S. A. Chen, Y. L. Chueh and J. H. He, Significant Efficiency Enhancement of Hybrid Solar Cells Using Core-Shell Nanowire Geometry for Energy Harvesting, *ACS Nano*, 2011, **5**, 9501–9510.
- 29 W. R. Wei, M. L. Tsai, S. T. Ho, S. H. Tai, C. R. Ho, S. H. Tsai, C. W. Liu, R. J. Chung and J. H. He, Above-11%-Efficiency Organic-Inorganic Hybrid Solar Cells with Omnidirectional Harvesting Characteristics by Employing Hierarchical Photon-Trapping Structures, *Nano Lett.*, 2013, **13**, 3658–3663.
- 30 K. K. Liu, W. Zhang, Y. H. Lee, Y. C. Lin, M. T. Chang, C. Y. Su, C. S. Chang, H. Li, Y. Shi and H. Zhang, Growth of Large-Area and Highly Crystalline MoS₂ Thin Layers on Insulating Substrates, *Nano Lett.*, 2012, **12**, 1538–1544.
- 31 Y. H. Lee, X. Q. Zhang, W. Zhang, M. T. Chang, C. T. Lin, K. D. Chang, Y. C. Yu, J. T. W. Wang, C. S. Chang and L. J. Li, Synthesis of Large-Area MoS₂ Atomic Layers with Chemical Vapor Deposition, *Adv. Mater.*, 2012, **24**, 2320–2325.
- 32 Y. C. Lin, W. Zhang, J. K. Huang, K. K. Liu, Y. H. Lee, C. T. Liang, C. W. Chu and L. J. Li, Wafer-Scale MoS₂ Thin Layers Prepared by MoO₃ Sulfurization, *Nanoscale*, 2012, **4**, 6637–6641.
- 33 K. Chang and W. X. Chen, l-Cysteine-Assisted Synthesis of Layered MoS₂/Graphene Composites with Excellent Electrochemical Performances for Lithium Ion Batteries, *ACS Nano*, 2011, **5**, 4720.
- 34 M. A. Hines and G. D. Scholes, Colloidal PbS Nanocrystals with Size Tunable Near Infrared Emission: Observation of Post Synthesis Self Narrowing of the Particle Size Distribution, *Adv. Mater.*, 2003, **15**, 1844–1849.
- 35 L. K. Jagadamma, M. Abdelsamie, A. E. Labban, E. Aresu, G. O. N. Ndjawa, D. H. Anjum, D. Cha, P. M. Beaujuge and A. Amassian, Efficient inverted bulk-heterojunction solar cells from low-temperature processing of amorphous ZnO buffer layers, *J. Mater. Chem. A*, 2014, **2**, 13321–13331.
- 36 C. H. Chuang, P. R. Brown, V. Bulovic and M. G. Bawendi, Improved performance and stability in quantum dot solar



- cells through band alignment engineering, *Nat. Mater.*, 2014, **13**, 796–801.
- 37 D. J. Late, B. Liu, H. S. S. R. Matte, C. N. R. Rao and V. P. Dravid, Rapid Characterization of Ultrathin Layers of Chalcogenides on SiO₂/Si Substrates, *Adv. Funct. Mater.*, 2012, **22**, 1894–1905.
- 38 M. Thripuranthaka, R. V. Kashid, C. S. Rout and D. J. Late, Temperature-dependent Raman spectroscopy of chemically derived few-layer MoS₂ and WS₂ nanosheets, *Appl. Phys. Lett.*, 2014, **104**, 081911.
- 39 R. Coehoorn, C. Haas, J. Dijkstra and C. J. F. Flipse, Electronic-Structure of MoSe₂, MoS₂, and WSe₂. I. Band-Structure Calculations and Photoelectron spectroscopy, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1987, **35**, 6195–6202.
- 40 L. A. King, W. Zhao, M. Chhowalla, D. J. Riley and G. Eda, Photo-electrochemical Properties of Chemically Exfoliated MoS₂, *J. Mater. Chem. A*, 2013, **1**, 8935–8941.

