



Cite this: *J. Mater. Chem. B*, 2019, 7, 5583

Received 28th June 2019,
Accepted 24th August 2019

DOI: 10.1039/c9tb01312a

rsc.li/materials-b

Layered double hydroxide nanostructures and nanocomposites for biomedical applications

Li Yan,^c Sevil Gonca,^b Guangyu Zhu,^{id e} Wenjun Zhang^{id d} and Xianfeng Chen^{id *ab}

Layered double hydroxide (LDH) nanostructures and related nanocomposites have attracted significant interest in biomedical applications including cancer therapy, bioimaging and antibacterial treatment. These materials hold great advantages including low cost and facile preparation, convenient drug loading, high drug incorporation capacity, good biocompatibility, efficient intracellular uptake and endosome/lysosome escape, and natural biodegradability in an acidic environment. In this review, we summarize the development of three types of LDH nanostructures including pristine LDH, surface modified LDH, and LDH nanocomposites for a range of biomedical applications. The advantages and disadvantages of LDH nanostructures and insights into the future development are also discussed.

1. Introduction

Layered double hydroxides (LDH) are a type of anionic clay with the formula generally expressed as $[M_{1-x}^{2+}M_x^{3+}(\text{OH})_2][A^{n-}]_{x/n} \cdot z\text{H}_2\text{O}$, where divalent cations M^{2+} are Mg^{2+} , Fe^{2+} , or Co^{2+} ; trivalent cations M^{3+} are Al^{3+} , Fe^{3+} , or Gd^{3+} ; and non-framework and exchangeable anions A^{n-} are Cl^- , CO_3^{2-} , NO_3^- , etc.^{1–5} (Fig. 1). LDH are positively charged because M^{2+} anions are partially substituted by M^{3+} . LDH nanostructures have been widely utilized for many applications, including energy, healthcare, catalysis and optics. This review will focus on the biomedical applications of LDH nanostructures and nanocomposites. Herein, we classify LDH nanostructures into 3 categories including pristine LDH nanostructures, surface modified LDH nanostructures including nanoparticles and recently reported nanosheets, and LDH nanocomposites. These LDH nanomaterials are useful for a range of biomedical applications (Fig. 2). For example: (1) $-\text{OH}$ groups make LDH sensitive to an acid environment and degrade easily in the biological environment to release loaded therapeutic molecules for bio-responsive drug delivery and (2) the positive charge of LDH



Fig. 1 Schematic illustration of LDH structure and chemical components⁶ (reproduced from The Royal Society of Chemistry with permission). (a) LDH nanoparticles⁷ (reproduced from Macmillan Publishers Limited with permission), (b) LDH nanosheets⁷ (reproduced from Macmillan Publishers Limited with permission), (c–f) LDH nanocomposites (reproduced from American Chemical Society, Springer, Elsevier and The Royal Society of Chemistry with permission).^{8–11}

^a Translational Medicine Center, The Second Affiliated Hospital, Guangzhou Medical University, Guangzhou, P. R. China

^b School of Engineering, Institute for Bioengineering, The University of Edinburgh, King's Buildings, Mayfield Road, Edinburgh EH9 3JL, UK.
E-mail: Michael.Chen@ed.ac.uk


^c Monash Institute of Pharmaceutical Sciences, Monash University, Parkville, Victoria 3052, Australia

^d Center of Super-Diamond and Advanced Films (COSDAF) and Department of Materials Science and Engineering, City University of Hong Kong, Hong Kong SAR, P. R. China

^e Department of Chemistry, City University of Hong Kong, Hong Kong SAR, P. R. China

allows the material to effectively interact with negatively charged cell membranes for efficient intracellular delivery. Due to the broad applications, LDH nanostructures are increasingly attractive and the synthesis, characterization and applications of LDH have undergone rapid development during the last decade.^{6–11} The number of



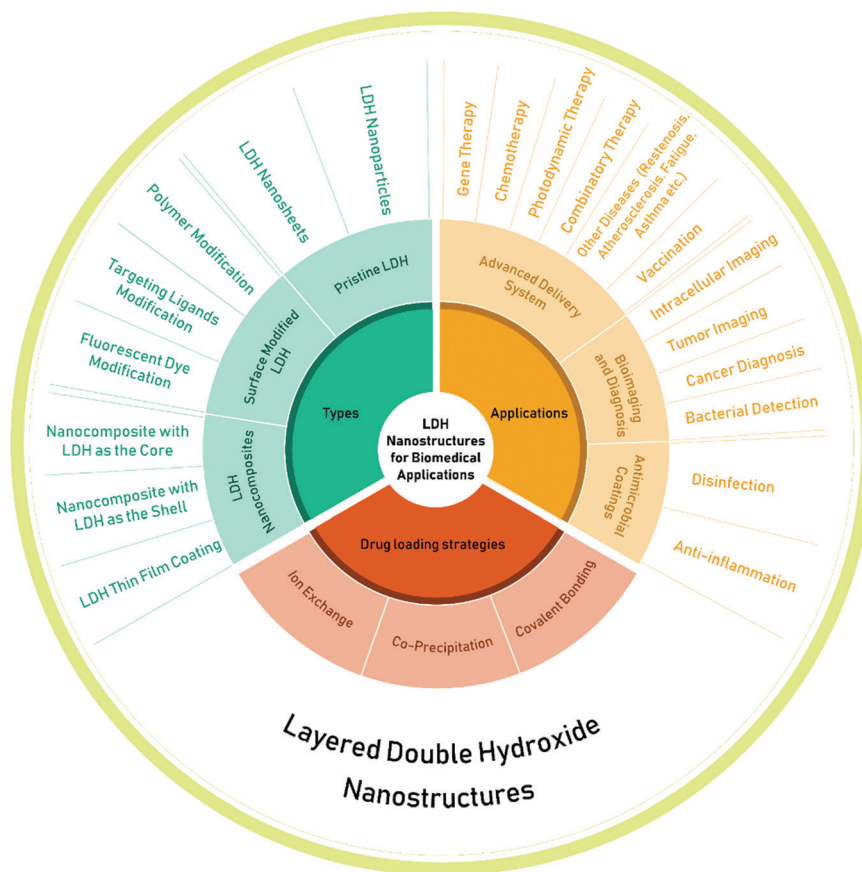

Pristine LDH nanoparticles were initially introduced for drug and gene delivery for cancer chemotherapy and then LDH nanostructures with different morphologies and geometries were developed for a wider range of applications. During this journey, to satisfy the requirements of advanced drug delivery systems and different biomedical applications, surface modified LDH nanostructures and LDH based nanocomposites have also been explored. In this review, we summarize and highlight the most important development of these three types of LDH nanostructures for biomedical applications, discuss about their advantages and disadvantages, and also provide our insights into the challenges and future applications of LDH nanomaterials.

Biological barriers in the human beings can effectively restrict hazardous agents and thus protect them from harmful diseases. As one of the most common biological barriers, the cell membrane can isolate, protect and regulate cells from the external environment.^{12–16} However, the fine and sophisticated structure of the cell membrane unavoidably and strictly prohibits the transport of drugs and genes

Pristine LDH nanoparticles were first introduced in the 2000s as a nonviral vector for biomolecule and deoxyribonucleic acid (DNA) delivery by Choy and co-workers.⁴⁷ In 2004, Choy *et al.* reported that pristine LDH nanoparticles could load negatively charged drug molecules for cancer therapy.⁴⁸ Methotrexate (MTX) was loaded into the interlayer space of LDH nanoparticles by mixing LDH with MTX at room temperature for 3 days through ion-exchange by replacing the NO₃ ions. After drug loading, the interlayer space of LDH nanoparticles expanded from 8.4 to 19.9 Å, but the structure and function of MTX and LDH nanoparticles were maintained without detectable change. The *in vitro* cell line test results showed that MTX-LDH nanoparticles were effective sooner than MTX alone. With 24 hours co-incubation of cell lines and drugs, the viability of

the cancer cells treated with MTX remained over 90%; in comparison, the viability of cells in the MTX-LDH treated group dropped to below 80%. Attractively, MTX-LDH nanoparticles effectively suppressed the proliferation of SaOS-2 cancer cells (osteosarcoma, human), but showed a negligible effect on normal cells (fibroblasts, human tendon). This work first demonstrated that LDH nanoparticles could act as a biocompatible non-viral vector for enhanced anti-cancer drug delivery.

The effectiveness of using LDH nanoparticles for drug delivery and the attractive cancer cell killing specificity were later demonstrated also in cisplatin prodrug delivery.⁴⁹ In terms of drug delivery effectiveness, disuccinatocisplatin (DSCP)-loaded LDH nanoparticles exhibited dramatically higher cytotoxicity than the free prodrug: the IC₅₀ value of DSCP against A2780 cancer cells was $1.75 \pm 0.20 \mu\text{M}$, while the value was $0.34 \pm 0.17 \mu\text{M}$ for LDH-Pt(IV) (LDH nanoparticles loaded with DSCP), indicating a 5-fold reduction of the IC₅₀ value (Table 1). With regard to cell specificity, LDH-Pt(IV) nanoparticles were significantly less effective towards the tested normal cells (NIH3T3, HS27 and BEAS-2B). For example, the IC₅₀ values of cisplatin and DSCP were 5.1 ± 0.8 and $30 \pm 2 \mu\text{M}$, respectively, while the value of LDH-Pt(IV) was over $50 \mu\text{M}$. These comparisons indicate that DSCP-loaded LDH nanoparticles are very effective in killing cancer cells, but relatively safe to healthy cells, which is ideal for anticancer drug design. To explain the cancer cell targeting specificity, the platinum content of cells was investigated after incubation with DSCP and DSCP-LDH. It was found that LDH-Pt(IV) could deliver 10-fold more drug to cells compared to DSCP alone.

Following the test in cell lines, Choi *et al.* studied MTX-LDH nanoparticles with an average diameter of 130 nm for *in vivo* cancer therapy.⁵⁰ Free MTX and MTX-LDH nanoparticles were intraperitoneally injected into two groups of mice bearing orthotopic human breast tumors. In the biodistribution analysis, it was discovered that the tumor–liver drug accumulation ratio of the MTX-LDH nanoparticle treated group was 6 times higher than that of the MTX-treated group. In line with this LDH nanoparticle enabled targeted delivery of MTX to the tumor, the antitumor efficacy of the nanoparticle treated group was significantly improved, indicated by 81.4% and 74.3% reductions of tumor volumes compared with that in the phosphate buffered saline (PBS) and free MTX group, respectively. This also shows that the efficacy of free drug is very low.

Besides cancer chemotherapy, LDH nanoparticles were also utilized as a photosensitizer vector for photodynamic therapy.

Duan and co-workers reported that the incorporation of zinc phthalocyanine (ZnPc) into the gallery of LDH nanoparticles resulted in high singlet oxygen production efficiency, improved photostability, good biocompatibility and low cytotoxicity.⁵¹ The *in vitro* test showed that a low dosage of ZnPc ($10 \mu\text{g mL}^{-1}$) caused potent damage to HepG2 cells with less than 15% viability. The *in vivo* investigation demonstrated that LDH nanoparticles effectively inhibited tumor growth with an ultra-low dose of 0.3 mg kg^{-1} and a low optical fluence rate of 54 J cm^{-2} . Recently, Mei *et al.* reported two-dimensional LDH monolayers with a diameter of 50 nm and a thickness of 0.8 nm for controlled loading and targeted delivery for cancer therapy.⁵² In this research, monolayered LDH nanosheets were loaded with the anti-cancer drug doxorubicin (DOX) with a high loading capacity of 3.6 mg mg^{-1} (DOX/LDH). The fabricated nanovectors, which could be further conjugated with the targeting agent folic acid, exhibited selective high toxicity towards cancer cells (KB cancer cells) and reduced toxicity to normal cells.⁵² Gao *et al.* developed a supramolecular photosensitizer (isophthalic acid/LDH nanohybrids) that could be activated by a near-infrared laser for efficient two-photon photodynamic therapy.⁵³ Upon 808 nm laser irradiation, this LDH based hybrid demonstrated significantly increased tissue penetration depth and was capable of killing cancer cells inside the tumor.⁵³

Beyond cancer therapy, LDH nanoparticles have also been applied to many other applications.⁵⁴ For example, to overcome the limitation of the short half-life of the anticoagulant drug low molecular weight heparin (LMWH), LMWH-LDH nanoparticles were fabricated *via* a co-precipitation method (adding drug simultaneously during the LDH nanoparticle preparation process, instead of preparing LDH nanoparticles first followed by drug loading *via* ion-exchange).⁵⁵ The *in vitro* release test indicated a biphasic and sustainable release profile of LMWH-LDH nanoparticles in pH 7.4 PBS solution at 37 °C. The liberation of the anticoagulant drug was 20% in the first 12 hours, followed by a further 20% release in the following 108 hours. The same group also found that LMWH-LDH nanoparticles had the potential to treat restenosis of an artery that occurs after surgically removing atherosclerotic lesions and restoring blood flow.⁵⁶ Restenosis is the recurrence of blood vessel narrowing. LMWH-LDH nanoparticles were tested on rat vascular smooth muscle cells (SMC); LMWH-LDH nanoparticles showed a higher ability to inhibit the migration and proliferation of SMC, with over 60% reduction of SMC compared with the control group (only growth medium). The enhanced efficacy of LMWH-LDH nanoparticles was explained as

Table 1 IC₅₀ values of cisplatin, DSCP, LDH-Pt(IV), and LDH in different cell lines⁴⁹ (reproduced from The Royal Society of Chemistry with permission)

Cell type	Cell line	Cisplatin [μM]	DSCP [μM]	LDH-Pt(IV) [μM]	LDH [mg L^{-1}]
Cancer	A549	5.0 ± 0.4	9.8 ± 0.2	0.84 ± 0.28	> 150
Cancer	A2780	0.45 ± 0.1	1.8 ± 0.2	0.34 ± 0.17	> 150
Cancer	NCI-H1299	3.3 ± 0.4	4.2 ± 0.7	0.71 ± 0.07	N.D.
Cancer	MCF-7	17 ± 1	> 25	1.9 ± 0.6	N.D.
Cancer	HCT116	3.7 ± 0.5	12 ± 1	0.49 ± 0.03	N.D.
Normal	NIH3T3	5.1 ± 0.8	30 ± 2	> 50	> 150
Normal	HS27	7.6 ± 0.7	35 ± 2	> 50	N.D.
Normal	BEAS-2B	2.7 ± 0.2	4.6 ± 0.9	23 ± 1	45





Fig. 3 Schematic diagram showing the proposed intracellular trafficking of LMWH-LDH nanoparticles in SMC. Both LMWH (A) and LMWH-LDH (B) are internalized by SMC via endocytosis; however, LMWH-LDH has the capacity of 'endosomal escape' preventing the degradation of LMWH in lysosomal compartments. LMWH-LDH and LMWH act to inhibit the MAPK pathway.⁵⁷ (Reproduced from Elsevier with permission.)


due to the higher cellular uptake through the endocytic pathway, quick escape from late endosomes/lysosomes, and effectively inhibited mitogen-activated protein kinase (MAPK) signal transduction over a prolonged period of time⁵⁷ (Fig. 3). LMWH delivery by LDH vectors was further improved by using antibody-targeted LDH nanoparticles for atherosclerosis.⁵⁸ In the system, an antibody (H93.7C.1D2/48; 1D2) was covalently conjugated to LMWH to form the 1D2-LMWH complex. Subsequently, this 1D2-LMWH complex was loaded into LDH nanoparticles *via* electrostatic interaction. The results showed that this nanodrug delivery system could be effectively transported to the arterial injury site with the aid of a targeting antibody, consequently achieving the sustained release of LMWH and resulting in minimized luminal loss and reduced thrombotic occlusion in a rat model of arterial injury.

Additionally, LDH nanoparticles were employed as an adjuvant to promote Th1 or Th2 dominant immune responses for vaccination purpose.⁵⁹ LDH nanoparticles were conjugated with a toll-like receptor ligand CpG, leading to significantly enhanced antibody response and a switch from Th2 towards Th1 response. On Day 21, LDH delivery induced significantly higher IgG2a antibody response than a standard commercial adjuvant Alum. Moreover, the animal test showed that immunization of mice with CpG-OVA-conjugated LDH nanoparticles before challenging with OVA-expressing B16/F10 tumor cells retarded tumor growth and prolonged the survival of tumor-bearing mice.⁵⁹ Furthermore, LDH nanoparticles loaded with the antigen Intimin β showed significantly enhanced uptake by antigen-presenting cells, promoting immune responses against infections by diarrheagenic *E. coli*.⁶⁰ LDH nanoparticles with Intimin β induced strong antibody- and cell-mediated immune responses, which maintained for at least four months in the mouse model with no changes in the histopathology of the animal organs.

Very recently, LDH nanoparticles were used for *in vivo* anti-fatigue by incorporating folic acid.⁶¹ LDH-folic acid constructs were fabricated *via* a co-precipitation method. It was found that the constructs were able to prolong the forced swimming time of the tested mice by 32% and 51% in comparison with the folic acid group and the control, with negligible cytotoxicity to normal cells. The forced swimming test was used to evaluate the mice's physical endurance capacity: reduced susceptibility to fatigue was correlated with longer swimming times.⁵⁶ Interestingly, it was also found that LDH-folic acid had an obvious effect on decreasing blood urea nitrogen and blood lactic acid, and increasing muscle and hepatic glycogen levels. These results indicated that LDH-folic acid effectively protected the body from fatigue. Wang *et al.* reported dexamethasone sodium phosphate (Dexa)-LDH nanoparticles for asthma treatment.⁶² In the allergic asthma rat model, this nanostructure effectively reduced inflammatory cells (macrophages, eosinophils and neutrophils) in the bronchoalveolar lavage (BAL) fluid, inhibited the increase of T-helper-2-type cytokines, and suppressed airway hyperresponsiveness.

For biomedical applications, it is essential for materials to have minimal toxicity. To know this, the bio-safety of LDH nanoparticles was investigated *in vivo*.⁶³ The study demonstrated that, when LDH nanoparticles were intravenously injected to Sprague Dawley rats at a dose of below 200 mg kg⁻¹, no obvious systemic side-effect could be observed in clinical chemistry and histopathology. This study confirmed the excellent biocompatibility of LDH nanoparticles and indicated their promising applications in biomedicine. The effectiveness and biocompatibility of LDH nanostructures can be controlled through various designs. When tested in mammalian cell lines,⁵⁹ it was found LDH nanostructures were rapidly uptaken by cells, and the shape had an influence on their



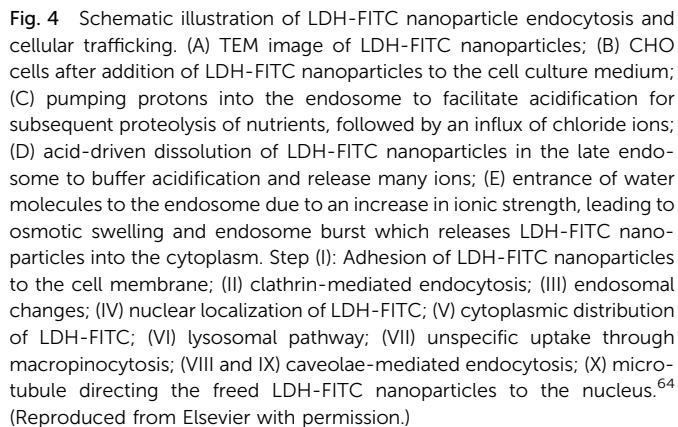

Gene therapy has attracted scientists and clinicians for treating diseases using therapeutic nuclei acids, such as DNA, small

For this, LDH nanoparticles have been developed to simultaneously transport two types of cancer treatment agents to improve cancer therapy and overcome drug resistance.⁹³ In one example, LDH nanoparticles were used as a vector to deliver the anticancer drug 5-Fluorouracil (5-Fu) and Allstars Cell Death siRNA (CD-siRNA) for potent cancer treatment.⁹⁴ The experiment outcomes proved

Fig. 5 (a) siRNA-LDH nanoparticles are internalized by clathrin-mediated endocytosis. Confocal images show a large number of brightly fluorescent puncta throughout the cytoplasm of neurons (arrowheads) and along their extended neurites (arrows) when incubated with siRNAeHtt6FAMELDH complexes (i). In the presence of chlorpromazine (CPZ) (an inhibitor of clathrin-mediated endocytosis) few 6FAM-positive vesicles are seen in the neurons (iii). However, faint 6FAM-positive puncta are visible at the plasma membrane (arrows). Panels (ii) and (iv) are the corresponding bright field images of panels (i) and (iii), respectively.⁸⁶ (Reproduced from Elsevier with permission.) (b and c) Images showing the extent of necrotic lesions on *N. tabacum* cv. Xanthi leaves challenged with PMMoV 5 days post spray treatment (b) and 20 days post spray treatment (c). * $p < 0.05$, ** $p < 0.01$ and *** $p < 0.001$ are significant using the Kruskal–Wallis test with a post-hoc Nemenyi test for multiple comparisons between samples compared with LDH. Data represent mean $\pm$ s.e.m.⁸⁷ (Reproduced from Macmillan Publishers Limited with permission.)

that the combined chemotherapy and gene therapy significantly enhanced the cytotoxicity of 5-Fu in three cancer cell lines (MCF-7, U2OS and HCT-116). In addition, LDH nanoparticles were reported to simultaneously load a Pt(IV) prodrug and a p53 activator.⁹⁵ It was discovered that the *in vitro* anticancer activity of cisplatin in p53-wild type cells was dramatically enhanced. The introduction of active p53 protein promoted apoptotic pathways initiated by platinum drugs, thereby substantially increasing the efficacy of the cisplatin prodrug (Fig. 6). Wang *et al.* co-loaded Pt(IV) prodrugs and the Chlorin e6 (Ce6) photosensitizer into LDH nanoparticles to overcome the drug resistance of cisplatin.⁹⁶ Ce6 photosensitizer and Pt(IV) prodrugs loaded LDH nanoparticles exhibited a synergistic effect in killing cancer cells, and particularly, were highly active towards

cisplatin-resistant cells, showing up to 190-fold increased efficiency in comparison with cisplatin alone. It is well known that the failure of cancer chemotherapy could be attributed to the escape of cancer cells from the immune system. In order to tackle this problem, Wang *et al.* fabricated a cisplatin-loaded immunochemotherapeutic LDH nanohybrid that bears an immune checkpoint inhibitor for enhanced cancer therapy⁹⁷ (Fig. 7). In the study, LDH nanoparticles were co-loaded with the first line chemotherapy drug cisplatin and the immune checkpoint inhibitor indoleamine-2,3-dioxygenase (IDO) inhibitor. The *in vitro* cervical cancer cell study revealed improved cellular accumulation, increased binding of Pt to DNA and higher apoptosis. The IDO inhibitor could inhibit indoleamine-2,3-dioxygenase and activate T cells, thus ultimately boosting the anti-tumor performance of the nanohybrid.⁹⁷

Most recently, LDH has been fabricated as a multifunctional drug carrier for theranostic applications.^{98–101} For instance, Li *et al.* reported pH-ultrasensitive Mn(II)-containing LDH nanoparticles with superb longitudinal relaxivity ($9.48 \text{ mM}^{-1} \text{ s}^{-1}$ at pH 5.0 and $6.82 \text{ mM}^{-1} \text{ s}^{-1}$ at pH 7.0 vs. $1.16 \text{ mM}^{-1} \text{ s}^{-1}$ at pH 7.4) for magnetic resonance imaging (MRI).¹⁰² A two-step method was utilized to synthesize Mn-LDH: Mg₃Al-LDH nanoparticles were first obtained through a co-precipitation method followed by isomorphic substitution of partial number of Mg²⁺ with Mn²⁺ ions (Fig. 8). The *in vivo* study revealed that Mn-LDH nanoparticles exhibited clear MRI for tumor tissues in mice for up to 2 days post intravenous injection, and also these nanoparticles were very promising for cancer diagnosis and treatment. Furthermore, Peng *et al.* prepared Gd³⁺-doped monolayered LDH nanosheets with controlled composition and morphology,¹⁰⁰


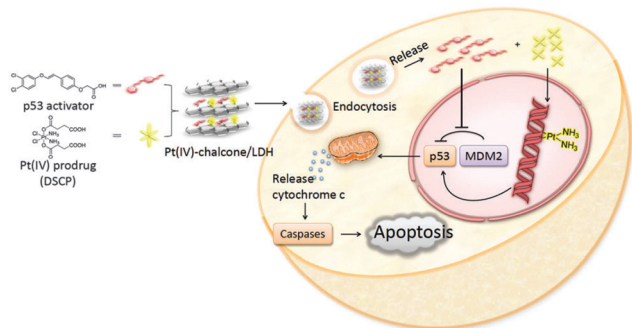


Fig. 6 Schematic illustration of co-delivery of a Pt(IV) prodrug and a p53 activator to enhance the anticancer activity of cisplatin⁹⁵ (reproduced from The Royal Society of Chemistry with permission).



For this purpose, surface modified and exfoliated layered gadolinium hydroxide nanoparticles were developed for use as multimodal contrast agents for MRI and fluorescence imaging.¹⁰⁸ In this material, LDH nanoparticles contain MR-active Gd^{3+} ions, which makes the material have potential for MRI. Then LDH nanoparticles were exfoliated by incorporation of long chain oleate ions, as shown in Fig. 9a. The separate individual layers were coated with phospholipids with poly(ethylene glycol) tail groups and fluorescent molecules to achieve multimodal imaging (MRI + fluorescence imaging) application *in vivo* (Fig. 9a). In another work, LDH nanoparticles were coated with liposome, enabling excellent water dispersion and sustained release characteristic, as shown in Fig. 9b.¹⁰⁹ Recently, the bovine serum albumin (BSA) pre-coating strategy was introduced to increase LDH nanoparticles' stability in buffered solution. This coating strategy could substantially prevent aggregation of LDH nanoparticles, and increase their cellular uptake in Chinese hamster ovary cells.¹¹⁰ Shi *et al.* fabricated bivalent cation $^{64}\text{Cu}^{2+}$ and trivalent cation $^{44}\text{Sc}^{3+}$ labelled LDH nanoparticles-BSA nanoparticles with excellent labelling efficiency and stability for *in vivo* positron emission tomography (PET).¹¹¹ In this work, PET imaging showed that prominent tumor uptake was achieved in 4T1 breast cancer with ^{64}Cu -LDH nanoparticles-BSA *via* passive targeting alone ($7.7 \pm 0.1\%$ ID g^{-1} at 16 h post-injection; $n = 3$). Zuo *et al.* modified LDH nanoparticles with brain tumor targeting ligands angiopep-2 and rabies virus glycoprotein.¹¹² The ligands were first covalently linked with BSA through the heterobifunctional cross-linker sulfosuccinimidyl 4-(*N*-maleimidomethyl)cyclohexane-1-carboxylate, and then coated onto the surface of LDH nanoparticles through electrostatic interaction, followed by cross-linking with the cross-linker glutaraldehyde to immobilize these BSAs on the LDH nanoparticles' surface. The ligand conjugated LDH nanoparticles showed dramatically enhanced cellular uptake by

and loaded the nanosheets with DOX (chemotherapy drug) and indocyanine green (photodynamic and photothermal agent) with a high loading content of 797.36% and an encapsulation efficiency of 99.67%. The *in vitro* and *in vivo* study demonstrated trimode (chemotherapy, photodynamic and photothermal therapy) synergetic anticancer activity with good biocompatibility. Meanwhile, Gd³⁺-doped monolayered LDH nanosheets could be utilized as dual mode imaging (near-infrared fluorescence and magnetic resonance imaging) agents to visualize the tumor site



Fig. 8 Schematic illustration of (a) the synthetic procedure and (b) structure related multifunctional properties of Mn-LDH nanoparticles.¹⁰² (Reproduced from Wiley-VCH Verlag GmbH & Co. KGaA with permission.)



Fig. 9 The surface modification approach for the fabrication of (a) exfoliated layered gadolinium hydroxide¹⁰⁸ (reproduced from Wiley-VCH Verlag GmbH & Co. KGaA with permission) and (b) liposome coated LDH¹⁰⁹ (reproduced from Elsevier with permission).

brain tumor cells, and increased the delivery efficacy of 5-FU for effective inhibition of neural U87 and N2a cells.


In addition to the above surface coating method which is mostly *via* electrostatic attraction, another approach is to modify LDH nanoparticles through covalent bonding by making use of the $-\text{OH}$ functional groups on the surface. Park *et al.* introduced (3-aminopropyl)triethoxysilane (APTES) to tailor

LDH nanoparticles through condensation between the hydroxyl groups of LDH and the ethoxy groups of APTES molecules to form a covalent bond.¹¹³ With this method, amine groups were grafted on the surface and interlayer spacing of LDH nanoparticles, making it convenient to attach other guest molecules. For example, the cancer cell specific ligand folic acid and fluorescein-5-isothiocyanate (FITC) were successfully conjugated onto the surface





Recently, it was reported that photosensitizer Ce6 could be covalently conjugated to PEG modified LDH nanoflakes.¹²⁰ In this study, Ce6 molecules were firmly anchored to the stabilized LDH nanoflakes and showed very slow release profiles of Ce6, avoiding premature release of drug molecules in blood and ensuring their efficient delivery to tumors. It was found that LDH nanoparticles–Ce6 significantly inhibited tumor growth as indicated by the size reduction to 13.4%, 14.3% and 26.9% of the tumor volume in the PBS, LDH–Ce6 Mix, and free Ce6 treated groups, respectively. In addition, LDH could be exfoliated to


Silica coating is one of the most commonly used methods to coat nanoparticles because of its ease of further functionalization, optical transparency, good hydrophilicity, excellent stability and high biocompatibility.^{123–128} Therefore, LDH nanoparticles were also decorated with a silica shell, using tetraethyl orthosilicate $\text{Si}(\text{OC}_2\text{H}_5)_4$ (TEOS) as a silica source.¹²² Initially, a surfactant template method was reported for an efficient synthesis of an LDH@ SiO_2 nanocomposite (Fig. 11a). In the method, CTAB was used as a surfactant-template to fabricate the LDH@ SiO_2 nanocomposite. The obtained nanostructures had uniform and accessible mesopores (~ 2.2 nm), high surface area (~ 430 m^2 g^{-1}), and large pore volume (~ 0.22 cm^3 g^{-1}). This nanocomposite was tested for a slow release of ibuprofen.¹²⁹ Then surfactants FC4 and F127 were also introduced to synthesize the LDH@ SiO_2 nanocomposite for sustained and pH sensitive release¹³⁰ (Fig. 11b). Li *et al.* used well-dispersed amine-functionalized SiO_2 nanodots to coat LDH by electrostatic interaction followed by condensation of APTES¹¹ (Fig. 11c). These LDH- SiO_2 dot nanostructures were well dispersible in cell culture medium and PBS buffer, and could be used to effectively deliver siRNA into U2OS cells.¹¹ Besides silica coating, a Gd-doped LDH@Au nanocomposite was fabricated for drug delivery and diagnosis.⁹ This nanocomposite system displayed high DOX loading capacity, and enabled a pH sensitive release profile of DOX. The Gd-doped LDH@Au nanocomposite was able to efficiently deliver DOX into cells, release DOX in the cytoplasm, and ultimately cause cancer cell death.⁹ Meanwhile, with Gd and Au doping, this nanocomposite could be employed for *in vitro* Computed Tomography (CT) and T1-weighted MR imaging, with

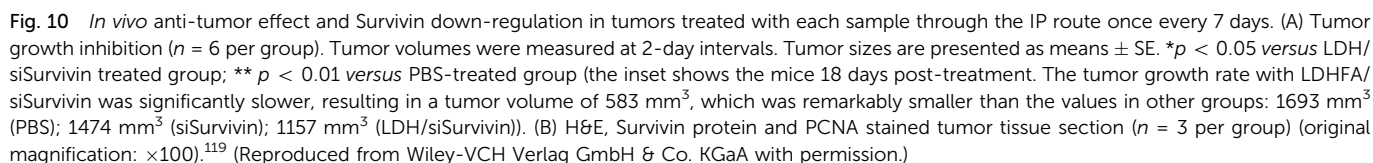

induced by an external magnetic field.^{132,133} This structure was then continued to be developed for cancer therapy.^{134,135} In one representative study, the anticancer agent doxifluridine was loaded to monodispersed strongly magnetic Fe₃O₄@LDH nanostructures. This Fe₃O₄@LDH nanocomposite had a well-defined core-shell structure, strong magnetization and magnetic guided controlled release properties.¹²³ For drug delivery, carboxyl group modified DOX was loaded to the LDH shell *via* anion-exchange¹³⁵ (Fig. 12). This DOX-COOH loaded nanocomposite exhibited high cytotoxicity and powerful inhibition towards cancer cells (HeLa cells), but had low toxicity to normal cells (HEK 293T Cells). The mechanism may be explained as follows: the acidic cytoplasm of HeLa cells stimulated rapid degradation of the LDH shell and converted DOX-COOH to positively charged DOX, thereby rapidly escaping from the positively

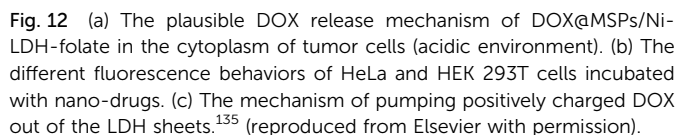

SiO₂ nanostructures were also encapsulated with a LDH shell. A 210 nm SiO₂@LDH core-shell nanocomposite was designed to enhance the immune adjuvant activity.¹³⁷ The zeta potential of this core-shell structure was 0.521 mV, making it easier for DNA binding compared with naked SiO₂ nanostructures which were negatively charged. The larger surface area of this nanocomposite can load a relatively large amount of DNA vaccine. Moreover, the SiO₂@LDH nanocomposite protected DNA from degradation, increased transfection efficiency, and efficiently promoted macrophage activation, compared with SiO₂ and LDH

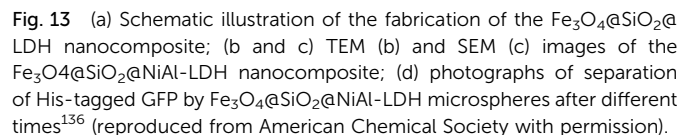

Au nanoparticles have also been employed as a core material, wrapped with LDH. In this work, MTX was first attached to citrate-stabilized Au nanoparticles; then, a SiO₂ layer was decorated on the surface of the Au nanostructure using tetraethyl orthosilicate (TEOS) as a silica source; later, NaOH was added to the SiO₂ shell; and finally, Mg²⁺ and Al³⁺ were added to the solution to obtain a LDH shell.¹⁴¹ By controlling the pH of SiO₂ etching, a core/shell structure (pH 11) or a yolk/shell structure (pH 10.5) was able to be controllably synthesized. MTX loaded to this nanostructure exhibited better anticancer efficiency, compared with free MTX and LDH-MTX.

LDH based film coating has been widely used for antimicrobial, sensing, electrochemical and optical applications.^{142–148} In a typical work, substrates including metals, ceramics, and glass were coated with oriented LDH films with strong adhesion. Subsequently, silver ions were *in situ* reduced to metallic silver nanoparticles and evenly distributed on the LDH surface¹⁴⁹ (Fig. 15a and b). The Ag-LDH coating showed excellent and durable antimicrobial activities against both Gram-negative (*E. coli* and *P. aeruginosa*) and Gram-positive (*B. subtilis* and *S. aureus*) bacteria¹⁴⁹ (Fig. 15c–g). Ciprofloxacin loaded LDH was also coated on a middle ear prostheses implant to combat

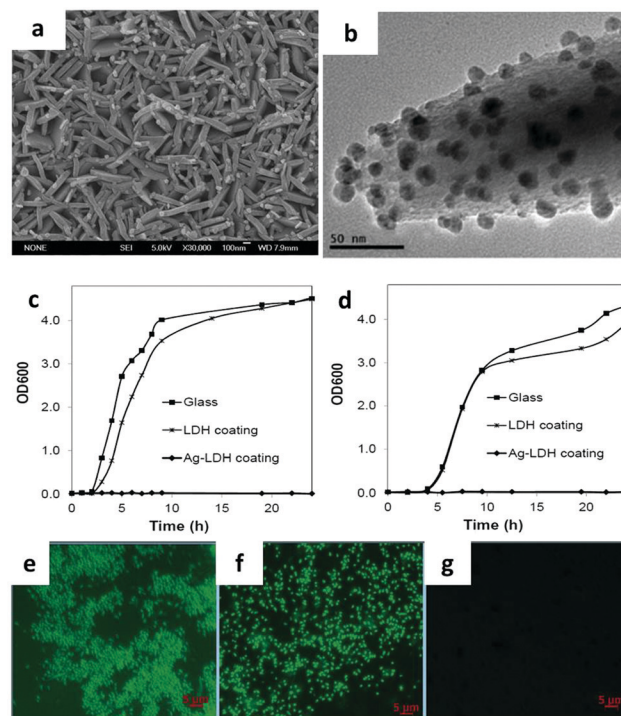


Fig. 15 (a) SEM image of Ag-LDH, (b) TEM image of Ag-LDH coating scraped from the substrate. (c and d) Bacterial growth curves of (c) *E. coli* and (d) *B. subtilis* in Luria-Bertani broth in the presence of the glass substrate, LDH coating and Ag-LDH coating on the glass substrates. (e–g) Confocal microscopy images of *E. coli* on the surface of (e) glass, (f) LDH coating, and (g) Ag-LDH coating after 24 h of culture (live cells stained green).¹⁴⁹ (Reproduced from Wiley-VCH Verlag GmbH & Co. KGaA with permission.)

CC BY

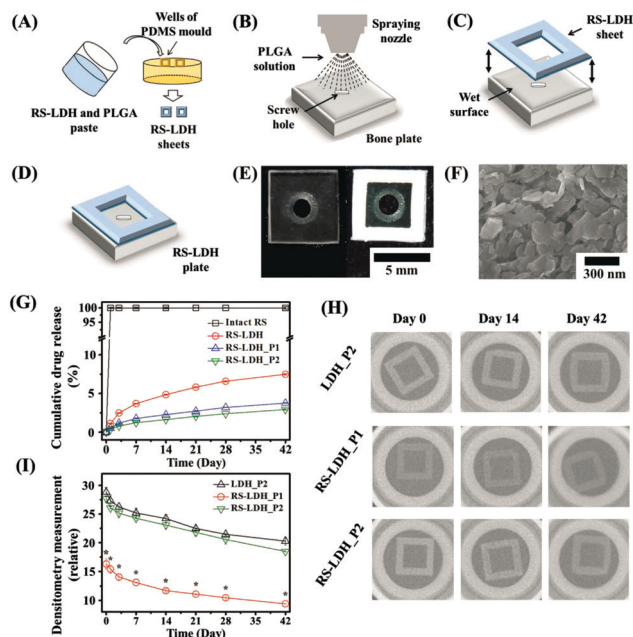


Fig. 17 Schematic preparation process of a theranostic plate. (A) RS-LDH sheets were separately prepared using polydimethylsiloxane (PDMS) molds consisting of square-shaped frames filled with a paste of RS-LDH and PLGA (5 : 1, w/w). (B) PLGA solution was sprayed onto the surface of a bone plate, and (C) the RS-LDH sheet was attached to the top to produce (D) the theranostic bone plate. (E) Optical images of the bioabsorbable bone fixation plates with and without a theranostic RS-LDH sheet. (F) FE-SEM image of the surface of a theranostic RS-LDH sheet. (G) *In vitro* drug-release profiles of the intact RS, RS-LDH, RS-LDH_P1, and RS-LDH_P2 in PBS (pH 7.4). (H) Representative *in vitro* X-ray images and (I) densitometry measurements of LDH_P2, RS-LDH_P1, and RS-LDH_P2 over 42 d. *RS-LDH_P1 differs significantly from both LDH_P2 and RS-LDH_P2 ($p < 0.05$).¹⁶⁷ (Reproduced from Wiley-VCH Verlag GmbH & Co. KGaA with permission.)

be incorporated for MRI observation. Compared with other materials such as semiconductor quantum dots for fluorescence imaging, MRI is much more clinically relevant.¹⁷² Third, LDH nanostructures are competent for cell membrane penetration due to their positive charge, thereby greatly improving intracellular delivery efficacy. Biological barriers are the major obstacles of effective delivery of drugs, genes and biomolecules into the cell cytoplasm.^{173,174} Fourth, the drug loading process can be very straightforward in the case of negatively charged species and the drug loading capacity is relatively high. Fifth, the fabrication is cheap and the size tunability can vary with a wide range from 20 nm to 10 μ m, suitable for different biological and clinical applications. This size tunability is far greater than for most other types of nanomaterials. Sixth, our research showed that ultra-thin LDH nanosheets tend to preferably accumulate in the kidney instead of liver like most other nanomaterials.¹²¹ This may be good for subsequent clearance and more suitable for clinical applications.^{175,176} Seventh, LDH has a great flexibility to form numerous types of composites for various utilizations. Furthermore, LDH is a type of ceramic nanoparticles with very high mechanical strength and therefore can be utilized as a filler to modify the mechanical strength of a polymer matrix for specific

applications and also as a thin film coating on various kinds of implantation devices.

5.2 Challenges of LDH nanostructures for biomedical applications

Although LDH nanostructures possess superior advantages that seem very promising for future applications, several challenges are still remaining. For example, because of the positive charge of LDH nanostructures, they may interact with negatively charge biomolecules in the biological environment and lead to loss of surface charge and aggregation. This challenge becomes crucial when LDH nanostructures are administrated *via* the blood system. Therefore, improvement of the stability of LDH nanostructures is a major challenge. Second, compared with other nanomaterials, there is less flexibility in functionalizing the surface of LDH nanostructures. For conventional LDH nanoparticles, due to the bulky thickness, the surface modification of the 2 outermost LDH layers is not enough for high stability in the biological environment. Therefore, it is important to develop new generations of ultra-thin LDH nanosheets with flexibility of surface modification for practical applications. Third, in comparison with other inorganic materials such as silica and gold nanoparticles, the controllability of the fabrication of LDH nanostructures and the reproducibility need to be substantially improved. To tackle this issue, continuous synthesis has been employed instead of the traditional flow chemistry approaches that allow reducing the residence time and maintaining almost constant supersaturation to produce LDH in large amounts.¹⁷⁷

6. Conclusions and future outlook

This review summarizes the development of LDH nanomaterials including pristine LDH nanostructures, surface modified LDH nanostructures, and LDH based nanocomposites for biomedical applications. LDH shows good biocompatibility, pH sensitivity, biodegradability, high intracellular delivery efficacy, and great flexibility in size tunability and nanocomposite formation. Initially, pristine LDH nanostructures were used for drug and gene delivery and photodynamic therapy. Although effective, it is desirable to surface modify these LDH nanostructures for improved properties due to the importance of the surface of nanomaterials. Surface modification not only makes LDH nanostructures more stable in buffer solution and blood system, but also enables versatile functions such as targeted delivery. Beyond using LDH nanostructures alone, there is great flexibility to combine LDH with many other materials such as metals, metal oxides, and polymers to further extend their functions and applications. It is expected that LDH nanomaterials have great potential in clinical applications due to their unique characteristics. In the future, the following aspects need to be explored to facilitate the application of LDH nanomaterials and their potential commercial use in the clinic. Firstly, it is essential to improve the synthesis approaches to produce highly uniform and reproducible LDH nanostructures with small variation in size, thickness, and geometry. Secondly, surface modification and drug loading under mild conditions

need to be established to ensure improved properties and minimize the influence of drug loading conditions such as temperature, time and pH on loaded drugs and genes. Thirdly, it is required to fabricate highly stable LDH nanomaterials in biological solution so that the drug delivery system can efficiently transport drugs and genes to target sites with minimal pre-mature drug and gene release. The high stability will prevent aggregation of nanostructures which can result in low therapeutic efficacy and possible precipitation in blood circulation. In this regard, it is desirable to develop ultra-thin LDH nanosheets. Fourthly, it is needed to thoroughly understand the *in vivo* biodegradability, biodistribution, and clearance of LDH nanomaterials. Fifthly, the flexibility of formation of LDH nanocomposites is an important advantage of LDH. This area of research should be significantly expanded, particularly by combining with materials which can circumvent the limitation of LDH nanostructures or enhance properties and performance. Moreover, there are many other types of nanostructures for biomedical applications such as bioceramic nanoparticles. However, there is a lack of studies that compare different types of nanomaterials with the same standard protocols for direct comparison so it is difficult to identify the best candidate for practical applications.

Conflicts of interest

There are no conflicts.

Acknowledgements

This work was financially supported by the General Research Fund of Hong Kong (GRF CityU Grant No. 11306717 and 11338516).

References

- 1 Z. P. Xu, G. Stevenson, C. Q. Lu and G. Q. Lu, *J. Phys. Chem. B*, 2006, **110**, 16923–16929.
- 2 Z. P. Xu, G. S. Stevenson, C. Q. Lu, G. Q. Lu, P. F. Bartlett and P. P. Gray, *J. Am. Chem. Soc.*, 2006, **128**, 36–37.
- 3 P. J. Sideris, U. G. Nielsen, Z. Gan and C. P. Grey, *Science*, 2008, **321**, 113–117.
- 4 Q. Wang and D. O'Hare, *Chem. Rev.*, 2012, **112**, 4124–4155.
- 5 L. Sheng, J. Y. Liu, C. Zhang, L. P. Zou, Y. Y. Li and Z. P. Xu, *Bioresour. Technol.*, 2019, **271**, 190–195.
- 6 R. J. Wang, W. J. Zhang, G. H. He and P. Gao, *J. Mater. Chem. A*, 2014, **2**, 16416–16423.
- 7 F. Song and X. L. Hu, *Nat. Commun.*, 2014, **5**, 4477.
- 8 M. Shao, F. Ning, J. Zhao, M. Wei, D. G. Evans and X. Duan, *J. Am. Chem. Soc.*, 2012, **134**, 1071–1077.
- 9 L. Wang, H. Xing, S. Zhang, Q. Ren, L. Pan, K. Zhang, W. Bu, X. Zheng, L. Zhou, W. Peng, Y. Hua and J. Shi, *Biomaterials*, 2013, **34**, 3390–3401.
- 10 J. C. Sun, J. J. Li, H. Fan and S. Y. Ai, *J. Mater. Chem. B*, 2013, **1**, 5436–5442.
- 11 L. Li, W. Y. Gu, J. Liu, S. Y. Yan and Z. P. Xu, *Nano Res.*, 2015, **8**, 682–694.
- 12 L. Yan, J. F. Zhang, C. S. Lee and X. F. Chen, *Small*, 2014, **10**, 4487–4504.
- 13 M. Elsabahy and K. L. Wooley, *Chem. Soc. Rev.*, 2012, **41**, 2545–2561.
- 14 E. Blanco, H. Shen and M. Ferrari, *Nat. Biotechnol.*, 2015, **33**, 941–951.
- 15 Y. Chen and L. Liu, *Adv. Drug Delivery Rev.*, 2012, **64**, 640–665.
- 16 Y. Wang, M. S. Shim, N. S. Levinson, H. W. Sung and Y. Xia, *Adv. Funct. Mater.*, 2014, **24**, 4206–4220.
- 17 L. Yan, Y. Yang, W. J. Zhang and X. F. Chen, *Adv. Mater.*, 2014, **26**, 5533–5540.
- 18 A. M. Wen and N. F. Steinmetz, *Chem. Soc. Rev.*, 2016, **45**, 4074–4126.
- 19 K. S. Sunderland, M. Yang and C. Mao, *Angew. Chem., Int. Ed.*, 2017, **56**, 1964–1992.
- 20 A. E. Czapar, Y. R. Zheng, I. A. Riddell, S. Shukla, S. G. Awuah, S. J. Lippard and N. F. Steinmetz, *ACS Nano*, 2016, **10**, 4119–4126.
- 21 S. J. Tseng, K. Y. Huang, I. M. Kempson, S. H. Kao, M. C. Liu, S. C. Yang, Z. X. Liao and P. C. Yang, *ACS Nano*, 2016, **10**, 10339–10346.
- 22 M. A. Kay, J. C. Glorioso and L. Naldini, *Nat. Med.*, 2001, **7**, 33–40.
- 23 D. W. Pack, A. S. Hoffman, S. Pun and P. S. Stayton, *Nat. Rev. Drug Discovery*, 2005, **4**, 581–593.
- 24 B. Gupta, T. S. Levchenko and V. P. Torchilin, *Adv. Drug Delivery Rev.*, 2005, **57**, 637–651.
- 25 S. Mura, J. Nicolas and P. Couvreur, *Nat. Mater.*, 2013, **12**, 991–1003.
- 26 N. M. Idris, M. K. Gnanasammandhan, J. Zhang, P. C. Ho, R. Mahendran and Y. Zhang, *Nat. Med.*, 2012, **18**, 1580–1585.
- 27 Z. J. Zhang, L. M. Wang, J. Wang, X. M. Jiang, X. H. Li, Z. J. Hu, Y. H. Ji, X. C. Wu and C. Y. Chen, *Adv. Mater.*, 2012, **24**, 1418–1423.
- 28 X. F. Chen and W. J. Zhang, *Chem. Soc. Rev.*, 2017, **46**, 734–760.
- 29 C. Chiappini, E. De Rosa, J. O. Martinez, X. Liu, J. Steele, M. M. Stevens and E. Tasciotti, *Nat. Mater.*, 2015, **14**, 532–539.
- 30 Y. Wang, Y. Yang, L. Yan, S. Y. Kwok, W. Li, Z. G. Wang, X. Y. Zhu, G. Y. Zhu, W. J. Zhang, X. F. Chen and P. Shi, *Nat. Commun.*, 2014, **5**, 4466.
- 31 E. Y. W. Chong, C. Y. P. Ng, V. W. Y. Choi, L. Yan, Y. Yang, W. J. Zhang, K. W. K. Yeung, X. F. Chen and K. N. Yu, *J. Mater. Chem. B*, 2013, **1**, 3390–3396.
- 32 X. F. Chen, G. Y. Zhu, Y. Yang, B. L. Wang, L. Yan, K. Y. Zhang, K. K. W. Lo and W. J. Zhang, *Adv. Healthcare Mater.*, 2013, **2**, 1103–1107.
- 33 X. Y. Zhu, M. F. Yuen, L. Yan, Z. Y. Zhang, F. J. Ai, Y. Yang, P. K. N. Yu, G. Y. Zhu, W. J. Zhang and X. F. Chen, *Adv. Healthcare Mater.*, 2016, **5**, 1157–1168.
- 34 Y. Chen, C. L. Tan, H. Zhang and L. Z. Wang, *Chem. Soc. Rev.*, 2015, **44**, 2681–2701.
- 35 Y. Zhang, B. Y. W. Hsu, C. L. Ren, X. Li and J. Wang, *Chem. Soc. Rev.*, 2015, **44**, 315–335.



- 36 P. P. Yang, S. L. Gai and J. Lin, *Chem. Soc. Rev.*, 2012, **41**, 3679–3698.
- 37 M. Zhang, Y. H. Zhao, L. Yan, R. Peltier, W. L. Hui, X. Yao, Y. L. Cui, X. F. Chen, H. Y. Sun and Z. K. Wang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 8834–8840.
- 38 K. Yang, L. Z. Feng, X. Z. Shi and Z. Liu, *Chem. Soc. Rev.*, 2013, **42**, 530–547.
- 39 L. Liu, Y. H. Tang, S. Dai, F. Kleitz and S. Z. Qiao, *Nanoscale*, 2016, **8**, 12803–12811.
- 40 J. F. Lin, J. Li, A. Gopal, T. Munshi, Y. W. Chu, J. X. Wang, T. T. Liu, B. Y. Shi, X. F. Chen and L. Yan, *Chem. Commun.*, 2019, **55**, 2656–2659.
- 41 X. Q. Chen, J. Sun, H. Zhao, K. Yang, Y. D. Zhu, H. R. Luo, K. Yu, H. S. Fan and X. D. Zhang, *J. Mater. Chem. B*, 2018, **6**, 3586–3599.
- 42 X. Q. Chen, Y. J. Tang, A. M. Liu, Y. D. Zhu, D. Gao, Y. Yang, J. Sun, H. S. Fan and X. D. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 14378–14388.
- 43 H. Zhao, C. H. Wu, D. Gao, S. P. Chen, Y. D. Zhu, J. Sun, H. R. Luo, K. Yu, H. S. Fan and X. D. Zhang, *ACS Nano*, 2018, **12**, 7838–7854.
- 44 H. Zhao, S. P. Chen, Y. H. He, C. H. Wu, Y. D. Zhu, K. Yu and H. S. Fan, *Nanoscale*, 2018, **10**, 11624–11632.
- 45 M. Lan, S. Zhao, W. Liu, C. S. Lee, W. Zhang and P. Wang, *Adv. Healthcare Mater.*, 2019, e1900132, DOI: 10.1002/adhm.201900132.
- 46 M. Lan, J. Zhang, Y. S. Chui, P. Wang, X. Chen, C. S. Lee, H. L. Kwong and W. Zhang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 21270–21278.
- 47 J. H. Choy, S. Y. Kwak, Y. J. Jeong and J. S. Park, *Angew. Chem., Int. Ed.*, 2000, **39**, 4042–4045.
- 48 J. H. Choy, J. S. Jung, J. M. Oh, M. Park, J. Jeong, Y. K. Kang and O. J. Han, *Biomaterials*, 2004, **25**, 3059–3064.
- 49 R. Ma, Z. G. Wang, L. Yan, X. F. Chen and G. Y. Zhu, *J. Mater. Chem. B*, 2014, **2**, 4868–4875.
- 50 G. Choi, O. J. Kwon, Y. Oh, C. O. Yun and J. H. Choy, *Sci. Rep.*, 2014, **4**, 4430.
- 51 R. Z. Liang, R. Tian, L. Ma, L. L. Zhang, Y. L. Hu, J. Wang, M. Wei, D. Yan, D. G. Evans and X. Duan, *Adv. Funct. Mater.*, 2014, **24**, 3144–3151.
- 52 X. Mei, S. M. Xu, T. Y. Hu, L. Q. Peng, R. Gao, R. Z. Liang, M. Wei, D. Evans and X. Duan, *Nano Res.*, 2018, **11**, 195–205.
- 53 R. Gao, X. Mei, D. P. Yan, R. Z. Liang and M. Wei, *Nat. Commun.*, 2018, **9**, 2798.
- 54 V. Rives, M. del Arco and C. Martin, *J. Controlled Release*, 2013, **169**, 28–39.
- 55 Z. Gu, A. C. Thomas, Z. P. Xu, J. H. Campbell and G. Q. Lu, *Chem. Mater.*, 2008, **20**, 3715–3722.
- 56 Z. Gu, B. E. Rolfe, Z. P. Xu, A. C. Thomas, J. H. Campbell and G. Q. Lu, *Biomaterials*, 2010, **31**, 5455–5462.
- 57 Z. Gu, B. E. Rolfe, A. C. Thomas, J. H. Campbell, G. Q. Lu and Z. P. Xu, *Biomaterials*, 2011, **32**, 7234–7240.
- 58 Z. Gu, B. E. Rolfe, Z. P. Xu, J. H. Campbell, G. Q. Lu and A. C. Thomas, *Adv. Healthcare Mater.*, 2012, **1**, 669–673.
- 59 S. Y. Yan, B. E. Rolfe, B. Zhang, Y. H. Mohammed, W. Y. Gu and Z. P. Xu, *Biomaterials*, 2014, **35**, 9508–9516.
- 60 W. Y. Chen, B. Zhang, T. Mahony, W. Y. Gu, B. Rolfe and Z. P. Xu, *Small*, 2016, **12**, 1627–1639.
- 61 L. L. Qin, W. R. Wang, S. H. You, J. M. Dong, Y. H. Zhou and J. B. Wang, *Int. J. Nanomed.*, 2014, **9**, 5701–5710.
- 62 W. R. Wang, A. Li, W. Mei, R. R. Zhu, K. Li, X. Y. Sun, Y. C. Qian and S. L. Wang, *RSC Adv.*, 2015, **5**, 23826–23834.
- 63 S. Y. Kwak, W. M. Kriven, M. A. Wallig and J. H. Choy, *Biomaterials*, 2004, **25**, 5995–6001.
- 64 Z. P. Xu, M. Niebert, K. Porazik, T. L. Walker, H. M. Cooper, A. P. J. Middelberg, P. P. Gray, P. F. Bartlett and G. Q. Lu, *J. Controlled Release*, 2008, **130**, 86–94.
- 65 S. Senapati, R. Thakur, S. P. Verma, S. Duggal, D. P. Mishra, P. Das, T. Shripathi, M. Kumar, D. Rana and P. Maiti, *J. Controlled Release*, 2016, **224**, 186–198.
- 66 L. Naldini, *Nature*, 2015, **526**, 351–360.
- 67 J. Kim, J. Kim, C. Jeong and W. J. Kim, *Adv. Drug Delivery Rev.*, 2016, **98**, 99–112.
- 68 L. Lambrecht, A. Lopes, S. Kos, G. Sersa, V. Preat and G. Vandermeulen, *Expert Opin. Drug Delivery*, 2016, **13**, 295–310.
- 69 K. Chatterjee, J. W. Chiu, H. Yu, P. S. Loh, A. Ghosh and V. Patzel, *Mol. Ther.*, 2019, **27**, 233.
- 70 H. Yin, R. L. Kanasty, A. A. Eltoukhy, A. J. Vegas, J. R. Dorkin and D. G. Anderson, *Nat. Rev. Genet.*, 2014, **15**, 541–555.
- 71 X. Du, C. X. Zhao, M. Y. Zhou, T. Y. Ma, H. W. Huang, M. Jaroniec, X. J. Zhang and S. Z. Qiao, *Small*, 2017, **13**, 1602592.
- 72 L. Xiong, J. X. Bi, Y. H. Tang and S. Z. Qiao, *Small*, 2016, **12**, 4735–4742.
- 73 L. Xiong and S. Z. Qiao, *Nanoscale*, 2016, **8**, 17446–17450.
- 74 H. B. Xia, Q. W. Mao, H. L. Paulson and B. L. Davidson, *Nat. Biotechnol.*, 2002, **20**, 1006–1010.
- 75 M. Jimenez-Sanchez, W. Lam, M. Hannus, B. Sonnichsen, S. Imarisio, A. Fleming, A. Tarditi, F. Menzies, T. E. Dami, C. Xu, E. Gonzalez-Couto, G. Lazzeroni, F. Heitz, D. Diamanti, L. Massai, V. P. Satagopam, G. Marconi, C. Caramelli, A. Nencini, M. Andreini, G. L. Sardone, N. P. Caradonna, V. Porcari, C. Scali, R. Schneider, G. Pollio, C. J. O’Kane, A. Caricasole and D. C. Rubinsztein, *Nat. Chem. Biol.*, 2015, **11**, 347–354.
- 76 S. Prakash, M. Malhotra and V. Rengaswamy, *Methods Mol. Biol.*, 2010, **623**, 211–229.
- 77 M. E. Davis, J. E. Zuckerman, C. H. J. Choi, D. Seligson, A. Tolcher, C. A. Alabi, Y. Yen, J. D. Heidel and A. Ribas, *Nature*, 2010, **464**, 1067–1070.
- 78 H. M. Liu, C. M. Qiao, J. Yang, J. Weng and X. Zhang, *J. Mater. Chem. B*, 2014, **2**, 5910–5924.
- 79 P. Y. Teo, C. Yang, L. M. Whilding, A. C. Parente-Pereira, J. Maher, A. J. T. George, J. L. Hedrick, Y. Y. Yang and S. Ghaem-Maghamsi, *Adv. Healthcare Mater.*, 2015, **4**, 1180–1189.
- 80 L. Zhou, Y. W. Xi, M. Chen, W. Niu, M. Wang, P. X. Ma and B. Lei, *Nanoscale*, 2019, **11**, 4614.
- 81 E. Crouchet, R. Saad, C. Affolter-Zbaraszczuk, J. Ogier, T. F. Baumert, C. Schuster and F. Meyer, *J. Mater. Chem. B*, 2017, **5**, 858–865.

- 82 L. Desigaux, M. Ben Belkacem, P. Richard, J. Cellier, P. Leone, L. Cario, F. Leroux, C. Taviot-Gueho and B. Pitard, *Nano Lett.*, 2006, **6**, 199–204.
- 83 S. D. Li, J. H. Li, C. J. Wang, Q. Wang, M. Z. Cader, J. Lu, D. G. Evans, X. Duan and D. O'Hare, *J. Mater. Chem. B*, 2013, **1**, 61–68.
- 84 Z. P. Xu, T. L. Walker, K. L. Liu, H. M. Cooper, G. Q. M. Lu and P. F. Bartlett, *Int. J. Nanomed.*, 2007, **2**, 163–174.
- 85 K. Ladewig, M. Niebert, Z. P. Xu, P. P. Gray and G. Q. M. Lu, *Biomaterials*, 2010, **31**, 1821–1829.
- 86 Y. Y. Wong, K. Markham, Z. P. Xu, M. Chen, G. Q. Lu, P. F. Bartlett and H. M. Cooper, *Biomaterials*, 2010, **31**, 8770–8779.
- 87 N. Mitter, E. A. Worrall, K. E. Robinson, P. Li, R. G. Jain, C. Taochy, S. J. Fletcher, B. J. Carroll, G. Q. Lu and Z. P. Xu, *Nat. Plants*, 2017, **3**, 16207.
- 88 J. A. Kemp, M. S. Shim, C. Y. Heo and Y. J. Kwon, *Adv. Drug Delivery Rev.*, 2016, **98**, 3–18.
- 89 D. Hughes and D. I. Andersson, *Nat. Rev. Genet.*, 2015, **16**, 459–471.
- 90 Y. Wen, W. Zhang, N. Q. Gong, Y. F. Wang, H. B. Guo, W. S. Guo, P. C. Wang and X. J. Liang, *Nanoscale*, 2017, **9**, 14347–14356.
- 91 Y. N. Wang, Y. H. Lu, J. Y. Zhang, X. F. Hu, Z. Y. Yang, Y. Guo and Y. B. Wang, *J. Mater. Chem. B*, 2019, **7**, 538–547.
- 92 B. B. Chu, F. Peng, H. Y. Wang, Y. Y. Su and Y. He, *J. Mater. Chem. B*, 2018, **6**, 7378–7382.
- 93 R. K. Kankala, P. Y. Tsai, Y. Kuthati, P. R. Wei, C. L. Liu and C. H. Lee, *J. Mater. Chem. B*, 2017, **5**, 1507–1517.
- 94 L. Li, W. Y. Gu, J. Z. Chen, W. Y. Chen and Z. P. Xu, *Biomaterials*, 2014, **35**, 3331–3339.
- 95 R. Ma, Y. P. Wang, L. Yan, L. L. Ma, Z. G. Wang, H. C. Chan, S. K. Chiu, X. F. Chen and G. Y. Zhu, *Chem. Commun.*, 2015, **51**, 7859–7862.
- 96 Z. G. Wang, R. Ma, L. Yan, X. F. Chen and G. Y. Zhu, *Chem. Commun.*, 2015, **51**, 11587–11590.
- 97 N. Wang, Z. G. Wang, Z. F. Xu, X. F. Chen and G. Y. Zhu, *Angew. Chem., Int. Ed.*, 2018, **57**, 3426–3430.
- 98 X. Mei, W. Wang, L. Yan, T. T. Hu, R. Z. Liang, D. Yan, M. Wei, D. G. Evans and X. Duan, *Biomaterials*, 2018, **165**, 14–24.
- 99 T. Y. Hu, J. He, S. M. Zhang, X. Mei, W. K. Zhang, R. Z. Liang, M. Wei, D. G. Evans and X. Duan, *Chem. Commun.*, 2018, **54**, 5760–5763.
- 100 L. Q. Peng, X. Mei, J. He, J. K. Xu, W. K. Zhang, R. Z. Liang, M. Wei, D. G. Evans and X. Duan, *Adv. Mater.*, 2018, **30**, 1707389.
- 101 W. S. Xie, Z. H. Guo, Z. B. Cao, Q. Gao, D. Wang, C. Boyer, M. Kavallaris, X. D. Sun, X. M. Wang, L. Y. Zhao and Z. Gu, *ACS Biomater. Sci. Eng.*, 2019, **5**, 2555–2562.
- 102 B. Li, Z. Gu, N. Kurniawan, W. Y. Chen and Z. P. Xu, *Adv. Mater.*, 2017, **29**, 1700373.
- 103 L. Yan, X. F. Chen, Z. G. Wane, X. J. Zhang, X. Y. Zhu, M. J. Zhou, W. Chen, L. B. Huang, V. A. L. Roy, P. K. N. Yu, G. Y. Zhu and W. J. Zhang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 32990–33000.
- 104 R. P. Wang, Z. S. He, P. J. Cai, Y. Zhao, L. Gao, W. Z. Yang, Y. L. Zhao, X. Y. Gao and F. P. Gao, *ACS Appl. Mater. Interfaces*, 2019, **11**, 13964–13972.
- 105 Z. H. Zhao, H. Kantamneni, S. Q. He, S. Pelka, A. S. Venkataraman, M. Kwon, S. K. Libutti, M. Pierce, P. V. Moghe, V. Ganapathy and M. C. Tan, *ACS Biomater. Sci. Eng.*, 2018, **4**, 2350–2363.
- 106 N. Yang, Y. P. Ding, Y. L. Zhang, B. Wang, X. Zhao, K. M. Cheng, Y. X. Huang, M. Taleb, J. Zhao, W. F. Dong, L. R. Zhang and G. J. Nie, *ACS Appl. Mater. Interfaces*, 2018, **10**, 22963–22973.
- 107 X. C. Gao, R. X. Cui, G. F. Ji and Z. L. Liu, *Nanoscale*, 2018, **10**, 6205–6211.
- 108 Y. S. Yoon, B. I. Lee, K. S. Lee, G. H. Im, S. H. Byeon, J. H. Lee and I. S. Lee, *Adv. Funct. Mater.*, 2009, **19**, 3375–3380.
- 109 Y. Zhang, H. Li, N. Du, S. Song and W. Hou, *Appl. Clay Sci.*, 2017, **143**, 336.
- 110 Z. Gu, H. L. Zuo, L. Li, A. H. Wu and Z. P. Xu, *J. Mater. Chem. B*, 2015, **3**, 3331–3339.
- 111 S. X. Shi, B. C. Fliss, Z. Gu, Y. A. Zhu, H. Hong, H. F. Valdovinos, R. Hernandez, S. Goel, H. M. Luo, F. Chen, T. E. Barnhart, R. J. Nickles, Z. P. Xu and W. B. Cai, *Sci. Rep.*, 2015, **5**, 16930.
- 112 H. L. Zuo, W. Y. Chen, H. M. Cooper and Z. P. Xu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 20444–20453.
- 113 A. Y. Park, H. Kwon, A. J. Woo and S. J. Kim, *Adv. Mater.*, 2005, **17**, 106–109.
- 114 J. M. Oh, S. J. Choi, G. E. Lee, S. H. Han and J. H. Choy, *Adv. Funct. Mater.*, 2009, **19**, 1617–1624.
- 115 P. R. Wei, S. H. Cheng, W. N. Liao, K. C. Kao, C. F. Weng and C. H. Lee, *J. Mater. Chem.*, 2012, **22**, 5503–5513.
- 116 Y. M. Kuo, Y. Kuthati, R. K. Kankala, P. R. Wei, C. F. Weng, C. L. Liu, P. J. Sung, C. Y. Mou and C. H. Lee, *J. Mater. Chem. B*, 2015, **3**, 3447–3458.
- 117 L. Yan, W. Chen, X. Y. Zhu, L. B. Huang, Z. G. Wang, G. Y. Zhu, V. A. L. Roy, K. N. Yu and X. F. Chen, *Chem. Commun.*, 2013, **49**, 10938–10940.
- 118 L. Yan, Y. Wang, J. H. Li, S. Kalytchuk, A. S. Sussha, S. V. Kershaw, F. Yan, A. L. Rogach and X. F. Chen, *J. Mater. Chem. C*, 2014, **2**, 4490–4494.
- 119 D. H. Park, J. Cho, O. J. Kwon, C. O. Yun and J. H. Choy, *Angew. Chem., Int. Ed.*, 2016, **55**, 4582–4586.
- 120 L. Yan, Z. G. Wang, X. F. Chen, X. J. Gou, Z. Y. Zhang, X. Y. Zhu, M. H. Lan, W. Chen, G. Y. Zhu and W. J. Zhang, *Chem. Commun.*, 2017, **53**, 2339–2342.
- 121 L. Yan, M. J. Zhou, X. J. Zhang, L. B. Huang, W. Chen, V. A. L. Roy, W. J. Zhang and X. F. Chen, *ACS Appl. Mater. Interfaces*, 2017, **9**, 34185–34193.
- 122 Z. Gu, J. J. Atherton and Z. P. Xu, *Chem. Commun.*, 2015, **51**, 3024–3036.
- 123 Q. Yue, Y. Zhang, Y. J. Jiang, J. L. Li, H. W. Zhang, C. Z. Yu, A. A. Elzatahry, A. Alghamdi, Y. H. Deng and D. Y. Zhao, *J. Am. Chem. Soc.*, 2017, **139**, 4954–4961.
- 124 Y. T. Niu, M. H. Yu, J. Zhang, Y. N. Yang, C. Xu, M. Yeh, E. Taran, J. J. C. Hou, P. P. Gray and C. Z. Yu, *J. Mater. Chem. B*, 2015, **3**, 8477–8485.

- Open Access Article. Published on 29 Difuu-sandaa 2019. Downloaded on 2025/11/30 7:58:42 PM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



- 170 J. F. Yu, Q. Wang, D. O'Hare and L. Y. Sun, *Chem. Soc. Rev.*, 2017, **46**, 5950–5974.
- 171 M. Pavlovic, P. Rouster, T. Oncsik and I. Szilagyi, *Chem-PlusChem*, 2017, **82**, 121–131.
- 172 B. R. Smith and S. S. Gambhir, *Chem. Rev.*, 2017, **117**, 901–986.
- 173 J. Z. Du, H. J. Li and J. Wang, *Acc. Chem. Res.*, 2018, **51**, 2848–2856.
- 174 M. Zheng, W. Tao, Y. Zou, O. C. Farokhzad and B. Shi, *Trends Biotechnol.*, 2018, **36**, 562–575.
- 175 M. X. Yu, J. Xu and J. Zheng, *Angew. Chem., Int. Ed.*, 2019, **58**, 4112–4128.
- 176 J. Q. Wang and G. Liu, *Angew. Chem., Int. Ed.*, 2018, **57**, 3008–3010.
- 177 D. Tichit, G. Layrac and C. Gerardin, *Chem. Eng. J.*, 2019, **369**, 302–332.

