



Cite this: *Green Chem.*, 2020, **22**, 6062

Using iron sulphate to form both n-type and p-type *pseudo*-thermoelectrics: non-hazardous and 'second life' thermogalvanic cells†

Mark A. Buckingham, , Kristine Laws, , Jason T. Sengel and Leigh Aldous *

Thermogalvanic cells can act like 'liquid thermoelectrics' to convert a thermal energy gradient to electrical energy. Such cells are typically combined electrically in-series in devices to boost the output voltage (as thermocells). However, the typical system involves a potentially fatal combination of inherently acidic or acidified $\text{Fe}^{2+/3+}$ and $[\text{Fe}(\text{CN})_6]^{3-/4-}$ electrolytes; mixing and heating is expected to trigger extremely toxic HCN gas release. Here we demonstrate that benign aqueous iron(II/III) sulphate can be combined with equally benign sodium sulphate and sodium hydrogen sulphate; the first leads to an $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ thermocell (Seebeck coefficient, $S_e = -0.4 \text{ mV K}^{-1}$), and the second to a thermocell with intermediate $[\text{FeSO}_4]^{0/+}$ and $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ character ($S_e = +0.57 \text{ mV K}^{-1}$). Their fundamental thermoelectrochemistry was explored, and their speciation elucidated. It was demonstrated that these can be utilised electrically in-parallel and in-series in thermogalvanic devices. When connected electrically in-series the thermocells presented here displayed temperature-dependent open circuit potentials only *ca.* one-third that typically reported for the 'conventional' combination of $\text{Fe}^{2+/3+}$ and $[\text{Fe}(\text{CN})_6]^{3-/4-}$ -based thermocells (0.8 mV K^{-1} vs. *ca.* 3 mV K^{-1} , respectively). However, whereas the latter thermocells cannot be safely mixed, when the iron-sulphate cells were 'accidentally' mixed they safely form a mixed thermocell electrolyte ($S_e = +0.19 \text{ mV K}^{-1}$), enabling a 'second life' of both the electrolyte and thermocell devices. This novel 'all-iron sulphate' thermocell was compared against the typically employed $\text{Fe}^{2+/3+}$ and $[\text{Fe}(\text{CN})_6]^{3-/4-}$ combination using the 12 principles of green chemistry and of green engineering, further demonstrating the inherent sustainability, safety and 'green' credentials of this system (but not yet efficiency). This work demonstrates how functionality and complexity can be introduced in a safe manner, while also preventing potential accidents and enabling new 'end-of-life' opportunities.

Received 2nd June 2020,
Accepted 18th August 2020
DOI: 10.1039/d0gc01878c
rsc.li/greenchem

Introduction

Both solid-state thermoelectric systems and liquid-state thermogalvanic systems exploit entropy; when exposed to a temperature difference across these systems they generate a flow of electricity.¹ Given that approximately two-thirds of the energy deliberately generated by mankind is currently lost as heat,² such devices present tremendous potential for improving global energy efficiency.

The magnitude of potential difference generated by these systems is typically quantified by the Seebeck coefficient, S_e .³ For thermoelectrics, this is given by eqn (1),³

$$\frac{\Delta V}{\Delta T} = -S_{e(\text{te})} \quad (1)$$

where ΔV is the potential difference generated when exposed to a temperature difference, ΔT , giving the thermoelectric Seebeck coefficient, $S_{e(\text{te})}$. The sign of the S_e shows the direction of current flow with respect to the temperature difference.^{3,4} A typical thermoelectric device requires two types of thermoelectric materials: one with a positive $S_{e(\text{te})}$ (electrons move from hot to cold; n-type conductor), the other with a negative $S_{e(\text{te})}$ (holes move from hot to cold; p-type).^{5,6} These are connected electrically in-series to boost the potential output, while ensuring the electrical connection is thermally in-parallel (to prevent a thermal short circuit across the device).^{4,5} Taking $S_{e(\text{te})}$ values on the order of $350 \mu\text{V K}^{-1}$ (typical of Bi_2Te_3 devices⁵), such a thermoelectric device would require *ca.* 285 pairs of n-p thermoelectrics in-series to generate 1 V at $\Delta T = 10 \text{ K}$. Such semiconductor devices are also typically composed of rare and toxic elements such as bismuth, lead, tin, selenium, silver, indium, gallium, germanium and tellurium;⁷ based upon current usage, all are classified as 'endangered elements' and face future supply limitations, with

Department of Chemistry, Britannia House, King's College London, London, SE1 1DB, UK. E-mail: leigh.aldous@kcl.ac.uk

†Electronic supplementary information (ESI) available. See DOI: 10.1039/d0gc01878c





UV-Vis and IR spectroscopy

All spectra were obtained using solutions containing either 0.03 M of the Fe(II) sulphate or 0.03 M of the Fe(III) sulphate, in the presence or absence of 0.075 M of either NaHSO₄ or Na₂SO₄. UV-Vis spectroscopy was performed using a Cary 100 UV-Vis and WinUV software (Agilent, UK) between 200–800 nm and with a UV-Vis crossover wavelength of 400 nm, at ambient temperature (*ca.* 20 °C), using quartz cuvettes with a path length of 100 μm (FireflySci, USA). IR spectroscopy was performed on the same solutions, using a droplet placed on a monolithic diamond ATR (Quest ATR Diamond accessory, Specac Ltd, UK) connected to an IRAffinity-1S Shimadzu spectrophotometer (Shimadzu, UK); results were obtained over 32 scans with a resolution of 4 cm⁻¹.



Results and discussion

Seebeck coefficient sign inversion in the iron sulphate system


Initially a stoichiometric aqueous mixture of iron(II) and iron(III) sulphate (0.3 M of each) was investigated. This mixture (abbreviated as [Fe(SO₄)]) yielded an apparent Seebeck coefficient (*aS_e*) of +0.27 mV K⁻¹ (shown in Fig. 1; blue circle in top left). This is slightly lower than previously reported values, with three similar un-acidified solutions also reporting *S_e* in

the range of +0.29 to +0.34 mV K⁻¹.^{4,16,22} This is likely due to this study using a higher concentration of [Fe(SO₄)] (which will reduce the *S_e*) and also due to not correcting the applied temperature difference to the experienced temperature difference (explained in the Experimental section). The values measured here are referred to as the 'apparent Seebeck coefficient' (*aS_e*) because they are only valid for the precise temperatures used (*T_c*, *T_h* and Δ*T*; explained in more detail below).

Next, acidification of the solution was explored. Acidified solutions of [Fe(SO₄)] have previously been used in thermogalvanic cells.^{4,15,16,22} Specifically the addition of H₂SO₄ to [Fe(SO₄)] thermocell solutions significantly increases the *S_e* (with reported values between +0.50 and +0.90 mV K⁻¹, depending upon concentration and pH),^{4,15,22} although notably this is below the *S_e* observed for un-acidified hexaaqua Fe^{2+/3+} solutions (between 1.35 and 1.66 mV K⁻¹).^{16,22} The *S_e* observed for hexaaqua Fe^{2+/3+} solutions are also slightly increased by acidification.²² These observations have been attributed to the hexaaqua species being partially susceptible to hydrolysis (exemplified by Fe³⁺ in eqn (3)), whereas the un-acidified [Fe(SO₄)] solutions demonstrate association of the Fe³⁺ with the sulphate dianion (eqn (4));^{16,22} this reduces the charge of the complex and hence lowers the *S_e*.⁴³



Acidification of the hexaaqua species shifts eqn (3) to the left, whereas acidification of [Fe(SO₄)] with H₂SO₄ is speculated to protonate the sulphate dianion (eqn (5)),²² increasing the fixed charge on the complex, and thus increasing the apparent *S_e*.

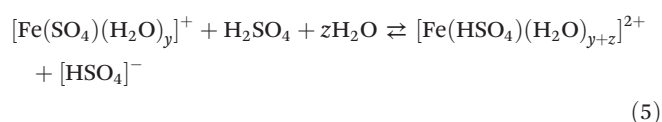

Since H₂SO₄ is highly corrosive and ecologically damaging if released into the environment,⁴⁴ the significantly more benign alternative sodium hydrogen sulphate (NaHSO₄) was explored. Notably, sodium (Na⁺), hydrogen sulphate ([HSO₄]⁻) and sulphate ([SO₄]²⁻) ions are all naturally abundant in water sources, including tap water.²² As shown in Fig. 1, addition of 1.5 M NaHSO₄ to the [Fe(SO₄)] system increased the *aS_e* from +0.27 mV K⁻¹ to +0.50 mV K⁻¹ (Fig. 1, red square). A concentration study demonstrated *aS_e* increased with increasing NaHSO₄ concentration (Fig. S1(d)†). While this change is not as significant as that achieved by the addition of 1 M H₂SO₄ (previously reaching up to +0.9 mV K⁻¹)²² it nevertheless demonstrates a new and less potentially hazardous route of enhancing the positive *S_e* of the [Fe(SO₄)] system.

Next, the effect of Na₂SO₄ addition was evaluated. As shown by the trend in Fig. 1, increasing concentrations of Na₂SO₄ in the [Fe(SO₄)] system resulted in a decrease in the *aS_e*, so much so that the system switched from a positive *aS_e* to a negative *aS_e*. The solubility limit of the system was reached by 1.5 M



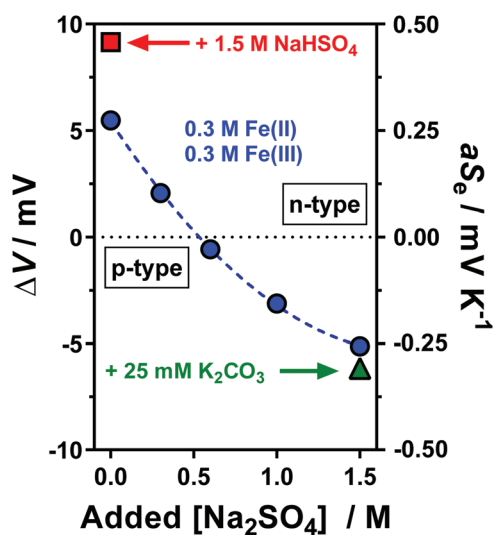


Fig. 1 Plot of the potential difference (Δ*V*) generated and corresponding apparent Seebeck coefficient (*aS_e*) when the thermocell was exposed to a temperature difference (Δ*T*) of 20 K. All systems contained 0.3 M Fe(II) and 0.3 M Fe(III) sulphate, with various Na₂SO₄ concentrations from 0 M to 1.5 M (as indicated by the x-axis), which resulted in inversion from a positive *aS_e* (equivalent to an n-type thermoelectric) to negative *aS_e* (p-type thermoelectric). Systems also containing either 1.5 M NaHSO₄ or 25 mM K₂CO₃ are indicated. The temperature applied to the colder electrode, *T_c*, was fixed at 20 °C. All values are the average of triplicate measurements; error bars (±1 standard deviation) were smaller than the size of the data point and so are not shown. The effect of iron sulphate concentration and NaHSO₄ concentration are shown in Fig. S1.†



Na₂SO₄, which gave an aS_e of -0.29 mV K^{-1} (shown in Fig. 1; blue circle in bottom right). This inversion in aS_e implies that the reduced species, Fe(II), now possesses a larger effective ionic charge than the oxidised species, Fe(III), such that reduction of Fe(III) to Fe(II) now occurs at the colder electrode in the thermocell. This is consistent with coordination of the iron cations with at least two $[\text{SO}_4]^{2-}$ groups, as shown in eqn (6) and (7) for Fe(II) and Fe(III), respectively (water of hydration omitted for clarity).



Whereas the positive aS_e systems became more positive upon acidification, the negative aS_e systems also became more negative upon addition of base, e.g. the addition of 25 mM K₂CO₃ increased the aS_e coefficient (Fig. 1, green triangle) from -0.26 to -0.31 mV K^{-1} . This is likely due to removal of some $[\text{HSO}_4]^-$ present in the system, and thus further increasing the concentration of $[\text{SO}_4]^{2-}$. However, iron is known to have a rich, pH-dependent chemistry,^{45,46} and Fe(III) precipitates $\geq \text{pH } 2.5$.⁴⁷ In this study, further addition beyond 1.5 M Na₂SO₄ and 25 mM K₂CO₃ resulted in rapid precipitation of the system.

The above observations are significant because they demonstrate that the Fe^{2+/3+} redox couple can be used as their relatively inexpensive and innocuous sulphate salts, and as-dissolved they yield a system roughly equivalent to $[\text{Fe}(\text{SO}_4)]^{0/+}$ ($aS_e = +0.27 \text{ mV K}^{-1}$). Minor acidification with 1.5 M NaHSO₄ increases the $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ character of the system ($aS_e = +0.50 \text{ mV K}^{-1}$), whereas the presence of 1.5 M Na₂SO₄ inverts the redox chemistry to give behaviour consistent with $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$, ($aS_e = -0.29 \text{ mV K}^{-1}$). Thus, if these systems can thermogalvanically generate electricity they could be used to prepare 'all-iron sulfate in-series' thermocells. Their ability to do this was therefore investigated.

Thermogalvanic current and power properties of the iron sulphate systems

The same systems explored in Fig. 1 were measured thermogalvanically, and their current and power output quantified. The short circuit current density (j_{sc}) produced by a single thermogalvanic cell (Fig. 2(a)) had the same trend as the aS_e (cf. Fig. 1); this makes sense since the aS_e is a major driving force in the current produced, as expressed by the Butler-Volmer equation.²³ The maximum electrical power produced, P_{max} , is given by $P_{max} = 0.25 \times aS_e \times j_{sc}$, and the investigated systems displayed a clear U-like trend (Fig. 2(b)); maximum power was produced at the extremes of the system, namely those with the largest absolute aS_e values, which in turn generated the larger absolute j_{sc} values and thus even larger P_{max} values. These results clearly demonstrate the various systems are able to generate electrical power *via* the thermogalvanic effect, but the direction and magnitude of the current flow is strongly influenced by the concentration of $[\text{SO}_4]^{2-}$ and $[\text{HSO}_4]^-$.

Temperature dependence of the thermoelectrochemistry

The thermogalvanic Seebeck coefficient for a system at a given concentration is generally a temperature-independent constant, which is unaffected by the temperature of the hotter electrode, the colder electrode and the temperature difference¹ (within reason). However, this does not apply if there are temperature-dependent equilibria present in the system.^{22,48}

Throughout the rest of this study, three systems were exclusively investigated: one containing 0.3 M Fe(II)[SO₄] and 0.3 M Fe(III)[SO₄]_{1.5} (the $[\text{Fe}(\text{SO}_4)]^{0/+}$ system), and another two based upon this but in addition containing 1.5 M NaHSO₄ ($[\text{Fe}(\text{HSO}_4)]^{+/2+}$) or 1.5 M Na₂SO₄ ($[\text{Fe}(\text{SO}_4)_2]^{-/2-}$), respectively. Systems containing K₂CO₃ were not explored further, given the additional complexity it introduced for only minor benefit. The thermogalvanic Seebeck coefficients for all three systems were measured under a range of conditions, and all three were found to be temperature sensitive; in particular, they were found to be most influenced by the temperature of the colder electrode, T_c . Fig. 3 displays the measured apparent

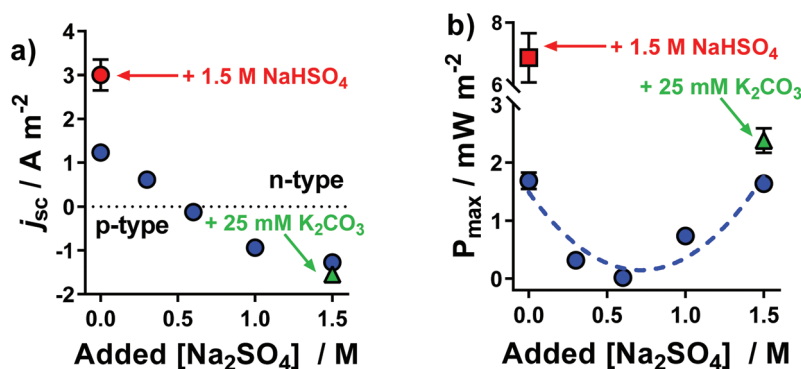


Fig. 2 Plots of the (a) short-circuit current density, j_{sc} , and (b) maximum power density, P_{max} , generated by the thermocells as a function of Na₂SO₄ concentration; all experimental conditions are the same as Fig. 1. All values are the average of triplicate measurements; error bars represent ± 1 standard deviation, and no error bars indicate error was equal to or smaller than the size of the data point. The effect of iron sulphate concentration and NaHSO₄ concentration are shown in Fig. S1.†



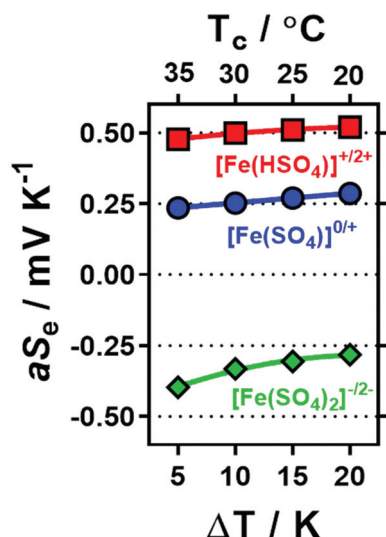


Fig. 3 Plot of the aS_e measured at four different ΔT values for 0.3 M Fe(III) and 0.3 M Fe(III) sulphate ($[\text{Fe}(\text{SO}_4)]^{0/+}$), and the same system but also containing 1.5 M NaHSO_4 ($[\text{Fe}(\text{HSO}_4)]^{+/2+}$) or 1.5 M Na_2SO_4 ($[\text{Fe}(\text{SO}_4)_2]^{-/2-}$). The aS_e corresponded to the measured ΔV and divided by the applied ΔT ; the ΔT was controlled by fixing $T_h = 40^\circ\text{C}$, and varying the applied T_c between 20°C and 35°C . Second order polynomial lines of best fit have been added to guide the eye of the reader, and are not intended to model the data.

Seebeck coefficients (aS_e) obtained at four different ΔT , achieved by varying T_c (Fig. S2† demonstrates the similar effect achieved when varying T_h); the fact that aS_e is not a constant value implies temperature-dependency, and explains why they have been referred to as ' aS_e ' rather than ' S_e ' throughout. The aS_e for all three systems became more negative at higher T_c values, which is indicative of a greater tendency to form ion pairs at elevated T values. This can be rationalised by considering the water of solvation: when solvated iron cations and solvated sulphate anions ion pair, several waters of solvation could be liberated with the result that ion pairing would be more entropically favoured, and would therefore increase with increasing T .

The $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ system displayed the highest degree of T sensitivity in Fig. 3, and this increased complexation at higher

T values also corresponded to higher aS_e values. These significant effects upon aS_e also significantly affected the j_{sc} and P_{max} produced by $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ thermocells. Fig. 4(a) displays the different aS_e values obtained when ΔT was fixed at 10 K, and the values of T_c and T_h simultaneously changed; upon increasing T_c from 20°C to 40°C , the aS_e value nearly doubled. This result is unusual, since typically a S_e value would remain constant or near-constant over such a narrow temperature range.⁴² As a result, the j_{sc} and P_{max} (Fig. 4(b) and (c), respectively) also increased significantly. We have recently reported a study in the same cell assembly using 0.2 M $\text{K}_3[\text{Fe}(\text{CN})_6]$ and 0.2 M $\text{K}_4[\text{Fe}(\text{CN})_6]$: fixing $\Delta T = 10$ K and increasing T_c from 20°C to 40°C did not change S_e significantly, but increased P_{max} 1.6-fold, primarily due to enhanced electron transfer kinetics and ion conduction.⁴² This T_c effect had an even more significant effect upon the more dynamic $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ system investigated here, with aS_e doubling and P_{max} increasing 5.5-fold (from 0.3 mW m^{-2} at $T_c = 20^\circ\text{C}$ to 1.66 mW m^{-2} at 40°C). Unfortunately apparatus limitations prevent us pushing the temperature range even further.

Spectroscopic investigation of the various iron sulphate solutions

In order to probe the potential species present, IR and UV-Vis spectroscopy were used to compare the $[\text{Fe}(\text{SO}_4)]^{0/+}$, $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ systems. For UV-Vis, only Fe(III) was investigated since any Fe(II) signals are typically obscured by the much stronger Fe(III) peaks;²² the solution also had to be diluted by an order of magnitude. The resulting UV-Vis spectra for all three systems are overlaid in Fig. 5; each system has two strong peaks in the ca. 220 nm and 300 nm regions, which have been previously attributed to the iron(III) hexaqua species and the $[\text{Fe}(\text{SO}_4)]^+$ species, respectively.^{16,22,49} Acidification with $[\text{HSO}_4]^-$ shifts the λ_{max} of both features, consistent with a shift in equilibrium (as shown by eqn (3) and (5), respectively). Conversely, addition of $[\text{SO}_4]^{2-}$ only resulted in a slight increase in the peak intensity attributed to the $[\text{Fe}(\text{SO}_4)]^+$ species. The UV-Vis results are therefore broadly consistent with the speculated interactions, but from these spectra we were unable to accurately determine the precise speciation.

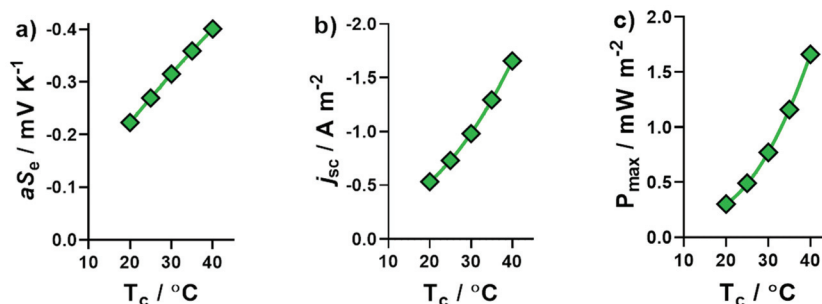


Fig. 4 Plots showing the significant effect different applied T_c values have upon the thermogalvanic properties of the $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ system, as quantified by the (a) aS_e , (b) j_{sc} , and (c) P_{max} . For all measurements $\Delta T = 10$ K, applied $T_h = T_c + 10^\circ\text{C}$, and applied T_c is indicated by the x-axis. Second order polynomial lines of best fit have been added to guide the eye of the reader, and are not intended to model the data.



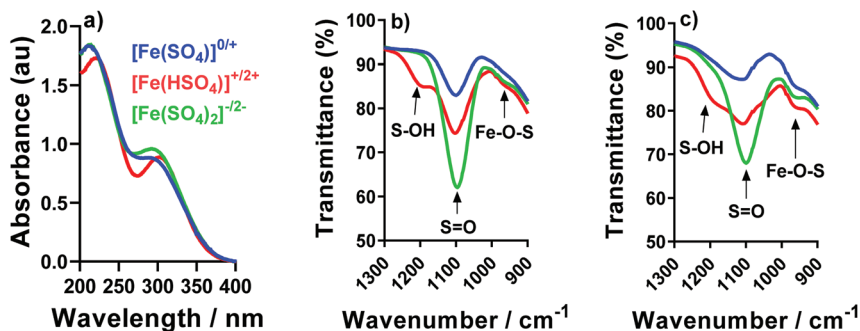


Fig. 5 Showing (a) UV-Vis spectra and (b and c) IR spectra of dilute analogues of the $[\text{Fe}(\text{SO}_4)]^{0/+}$ (blue lines), $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ (red lines) and $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$ (green lines) systems. Note that all used 0.03 M iron sulphate in a single oxidation state, plus 0.075 M $\text{Na}_2\text{SO}_4/\text{NaHSO}_4$ (as applicable); (a) and (c) used 0.03 M iron(III) sulphate, and (b) used 0.03 M iron(II) sulphate.

IR was also employed in an attempt to probe the speciation; in previous IR studies a $[\text{SO}_4]^{2-}$ peak has been reported to be centred at 1100 cm^{-1} , but is known to be highly pH-dependent between pH 1 and 3, and significantly affected by the ionic strength.⁴⁷ Fig. 5(b) and (c) shows the IR spectra for the Fe(II) and Fe(III) systems, respectively; both exhibit peaks at 1100 cm^{-1} corresponding to the asymmetric stretches of the $[\text{SO}_4]^{2-}$ ion. All Fe-containing systems possessed small shoulders in the ca. 980 cm^{-1} region, which were absent from Fe-free solutions (e.g. only Na_2SO_4 and NaHSO_4 , as shown in the ESI in Fig. S3†). These features have previously been assigned to distortion of the $[\text{SO}_4]^{2-}$ upon complexation with Fe;⁴⁷ this is tentatively attributed here to the resulting Fe–O–S stretch. These shoulders/peaks which are related with Fe–O–S stretching (which is indicative of complexation of the $\text{Fe}^{2+/3+}$ metal centre with $[\text{SO}_4]^{2-}$ anions) increased for both Fe(II) and Fe(III) after the addition of Na_2SO_4 or NaHSO_4 , which is consistent with eqn (7); these features were significantly more pronounced in the Fe(III) systems. Furthermore, addition of $[\text{HSO}_4]^-$ resulted in growth of a new peak at ca. 1200 cm^{-1} , which has previously been attributed to the S–O–H stretch in the $[\text{HSO}_4]^-$ ion.⁴⁷

The IR results present evidence of interaction of the $[\text{SO}_4]^{2-}$ and $[\text{HSO}_4]^-$ anions with both the Fe(II) and Fe(III) cations, supporting the earlier thermogalvanic analysis which indicated complicated equilibria and interactions between species are present. However, since the above UV-Vis and IR results only yielded qualitative evidence of association, a more quantitative investigation of the thermoelectrochemical data was performed.

Thermoelectrochemical determination of speciation within the thermocell

Previously, Weaver *et al.* have demonstrated that the difference in entropy of a simple redox couple (ΔS_{rc}) is directly proportional to $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$, where Z is the ionic charge of the species and r is the average ionic radius.^{43,50} The ΔS_{rc} is given by the aS_e , as shown by eqn (2).

In order to test the validity of this model for the aqueous Fe(II)/Fe(III) redox system, the literature values of ΔS_{rc} and

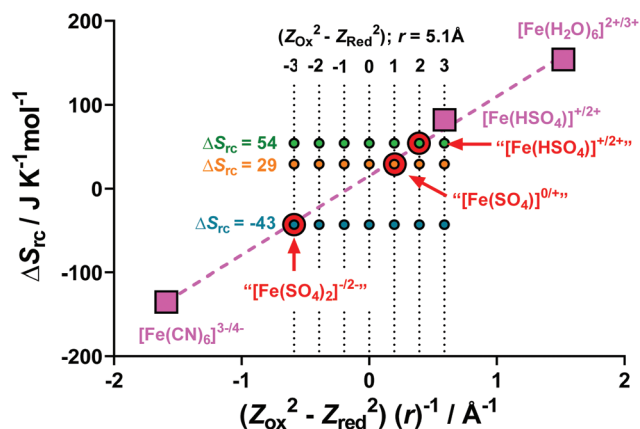


Fig. 6 Plot of ΔS_{rc} vs. $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$ for previously reported Fe(II)/Fe(III) redox systems (pink squares) and the three Fe(II)/Fe(III) redox systems investigated here (red circles). Also shown are different calculated values of $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$ where r was fixed as 5.1 Å , and $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$ varied, in order to quantify which $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$ values best represent the $[\text{Fe}(\text{SO}_4)]^{0/+}$, $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$ systems investigated here.

$(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$ were used for $[\text{Fe}(\text{H}_2\text{O})_6]^{2+/3+}$,²² $[\text{Fe}(\text{CN})_6]^{3-/4-}$,¹⁰ and $[\text{Fe}(\text{HSO}_4)]^{+/2+}$,²² (values tabulated in Table S2†). These values have been plotted in Fig. 6 (pink squares), and the expected linear relationship was observed (dashed pink line).

Next, we calculated the ΔS_{rc} for our systems, namely $[\text{Fe}(\text{SO}_4)]^{0/+}$, $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$ (tabulated in Table S2†). Knowing the value corresponding to the y-axis, these 3 systems were plotted on Fig. 6 (indicated by red circles) using the linear $y = mx + c$ relationship as given by the three known and previously reported systems. From this fit, the x-axis value (i.e. $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$) for the three systems could be estimated.

A value of 5.1 Å was estimated as r for all three systems;† knowing r , seven possible $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$ values were calculated,

† The ionic radius of the species (r) was calculated from the ionic radius of the ions and postulated species present. This calculation is fully discussed in the ESI,† along with a demonstration of the effect of changing r for the determination of the species present in the system.



and these potential ($Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$)/ r are shown on Fig. 6 as a 7×3 array. Notably, all three experimentally determined ΔS_{rc} values fit three hypothetical ($Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$) values, corresponding to -3 , $+1$ and $+2$ for the $[\text{Fe}(\text{SO}_4)_2]^{-2-}$, $[\text{Fe}(\text{SO}_4)]^{0/+}$ and $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ systems, respectively.

The -3 and $+1$ scenarios correlate excellently with proposed species present in the “ $[\text{Fe}(\text{SO}_4)_2]^{-2-}$ ” system (*i.e.* -1^2 to $-2^2 = -3$) and the “ $[\text{FeSO}_4]^{0/+}$ ” system (*i.e.* $+1^2$ to $0^2 = +1$), respectively. However, the ($Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$) = $+2$ scenario for the proposed “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system does not correspond to any possible combination of Z_{Ox} and Z_{Red} integers. Furthermore, the aS_e for the “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system generated here (using NaHSO_4) is lower than the literature value reported for a $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ system, which was achieved by acidification with a large excess of H_2SO_4 .^{4,22} Therefore the “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system investigated here using NaHSO_4 likely has intermediate character between the $[\text{FeSO}_4]^{0/+}$ and $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ systems, either as an unknown species, or more likely due to the aS_e being a mixed potential corresponding to a number of distinct species in solution, *e.g.* $[\text{FeSO}_4]^{0/+}$ or $[\text{Fe}(\text{HSO}_4)]^{+/2+}$. This is likely due to the less acidic nature of NaHSO_4 , relative to H_2SO_4 (pK_a values of H_2SO_4 and $[\text{HSO}_4]^-$ are -3 and 1.99 , respectively⁵¹).

With the speciation in the three interrogated thermocells determined, the redox chemistry of the three systems needed to be further investigated; this was performed with cyclic voltammetry and electrochemical impedance spectroscopy.

Cyclic voltammetry and electrochemical impedance spectroscopy

Cyclic voltammograms (CVs) of the $[\text{Fe}(\text{SO}_4)_2]^{-2-}$, $[\text{Fe}(\text{SO}_4)]^{0/+}$ and $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ systems were measured (Fig. 7). CVs of such highly concentrated and unsupported solutions (*e.g.* $0.6 \text{ M Fe(II)/Fe(III)}$), with no large excess of added supporting electrolyte leads to non-ideal responses, but is consistent with other thermoelectrochemical investigations.²² All three systems gave the expected reversible electrochemistry, although notably the $[\text{Fe}(\text{SO}_4)]^{0/+}$ system had a significantly larger peak-to-peak sep-

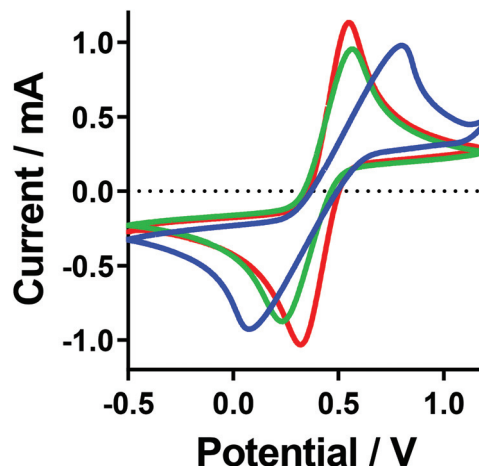


Fig. 7 Cyclic voltammograms recorded for the $[\text{Fe}(\text{SO}_4)]^{0/+}$ (blue line), $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ (red line) and $[\text{Fe}(\text{SO}_4)_2]^{-2-}$ (green line) systems. All recorded at ambient temperature using an Au working electrode, vs. an Ag/AgCl reference electrode, at 100 mV s^{-1} . A table of data for the values can be found in the ESI.†

aration than the other two (following the trend $[\text{Fe}(\text{SO}_4)]^{0/+} \gg [\text{Fe}(\text{SO}_4)_2]^{-2-} > [\text{Fe}(\text{HSO}_4)]^{+/2+}$), which increased significantly with scan rate (Fig. S5†). This could have arisen due to either uncompensated resistance and/or slower electron transfer rates; electrochemical impedance spectroscopy was therefore employed to quantify these aspects.

Electrochemical impedance analysis was performed *in situ* in the thermocell, where the hot electrode was used as the working electrode, and the cold electrode as the counter and a Pt wire *pseudo*-reference; please note that during these measurements the cell was not generating power. These experiments were repeated with the cold electrode as the working electrode, and the same trends were observed; all impedance results can be found in the ESI.† The impedance spectra were modelled in order to determine the solution (or mass trans-

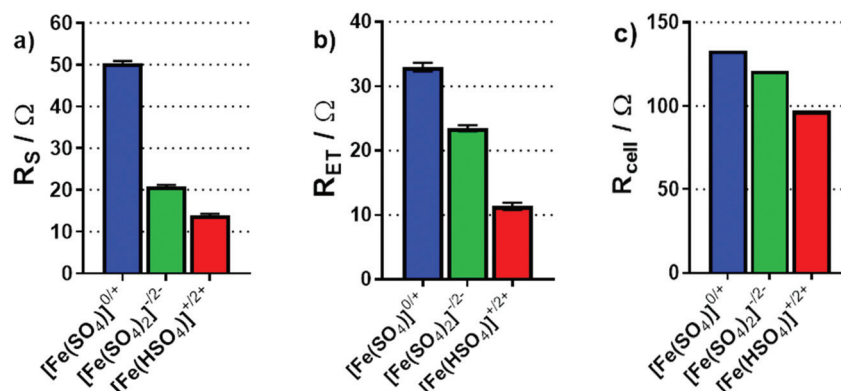


Fig. 8 Bar charts summarising (a) the solution resistance, R_s and (b) the electron transfer resistance, R_{ET} , determined through impedance spectroscopy in the non-isothermal thermocell. Also shown is (c) the calculated total thermocell resistance, R_{cell} of the thermogalvanic cell during steady-state discharge, based upon Ohm's Law ($V = IR$) from I - V plots during power production. All measurements were taken at an applied ΔT of 20 K ($T_c = 20^\circ \text{C}$). For EIS analysis, the spectra are included in the ESI,† and the fitting model has been previously reported elsewhere.²²



port) resistance (R_s) and electron transfer resistance (R_{ET}). Fig. 8(a) and (b) display the results for the R_s and R_{ET} of the three investigated systems; both display a trend of decreasing resistance going from $[\text{Fe}(\text{SO}_4)]^{0/+}$ to $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ to $[\text{Fe}(\text{HSO}_4)]^{+/2+}$. The significantly higher R_s for $[\text{Fe}(\text{SO}_4)]^{0/+}$ is consistent with the CVs, and the two other systems having a significantly higher ionic strength, whereas the abnormally high mobility of H^+ accounts for $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ having the lowest R_s value. The trend in R_{ET} follows the same order, but is less easy to explain; further work is required to determine if this is related to speciation, the electrode surface chemistry, or due to other changes (such as in the electrochemical double layer). However, the same trend was also observed at graphite electrodes (discussed later).

The overall resistance of the thermocell (R_{cell}) during steady-state thermogalvanic discharge can also be calculated from the gradient of the I - V plots measured for the three systems (from the $V = IR$ relationship). Fig. 8(c) plots these values, which also follow the same trend as P_{max} , R_s and R_{ET} . Notably, the R_{cell} calculated from thermogalvanic power measurements are higher than the sum of the R_s and R_{ET} values, which relate to an additional mass transfer resistance of the redox active species, as well as possible changes in R_s and R_{ET} during steady-state power generation; thermogalvanic cells which have achieved genuine steady-state⁴² possess a concentration gradient,¹⁰ given the active redox chemistry occurring at the two electrodes.

In-parallel and in-series thermocell devices

Individual thermocells can only generate a modest potential from modest temperature gradients. This is due to the limited Seebeck coefficients (in the 0.1–1.5 mV K⁻¹ range).^{4,22} A solution to this is to combine several so-called n- and p-type thermocells (+ve and -ve S_e values, respectively) and arrange them electrically in-series but thermally in-parallel; this increases the total potential,^{14–17} whilst avoiding a thermal short circuit.⁴ This was therefore demonstrated, initially by combining the $[\text{Fe}(\text{SO}_4)]^{0/+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ systems.

Fig. 9(a) displays the power curves for individual $[\text{Fe}(\text{SO}_4)]^{0/+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ thermocells, as well as the power curve generated when combined in-series. The generated potential was nearly the sum of the two potentials, as expected; it reached only 95% of the sum due to the increased resistance of the thermocell due to the additional electrical connections.⁴ While the overall power output can in theory be doubled by connecting thermocells in series,⁴ here total P_{max} increased only by a factor of 1.9 (rather than 2.0) due to the internal resistance mentioned above.

Next, the same was performed but with the $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ thermocells; these two have a significantly bigger discrepancy in P_{max} , as shown in Fig. 9(b). Despite this, the potential output still essentially doubled (97% of the sum), while the overall P_{max} was 94% of the sum of two P_{max} (a factor of 1.1 with respect to $[\text{Fe}(\text{HSO}_4)]^{+/2+}$, but a factor of 5.4 with respect to $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$). This demonstrated how these systems could be combined to significantly increase the

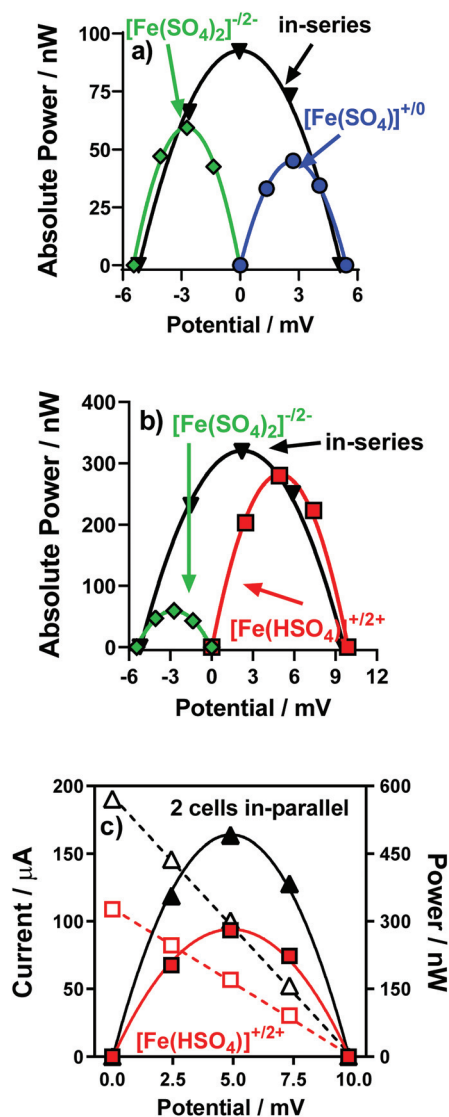


Fig. 9 Power curves measured for individual thermocells and electrically in-series thermocells for (a) $[\text{Fe}(\text{SO}_4)]^{0/+}$ (blue circles) and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ (green diamonds), and for (b) $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ (red squares) and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ (green diamonds). The in-series data for (a) and (b) (black inverted triangles) is offset on the x-axis to demonstrate how the potential is additive. Also (c) the power curves (filled symbols; solid lines) and I - V data (hollow symbols; dashed lines) measured for an individual $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ thermocell (red squares) and two $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ thermocells electrically in-parallel (black triangles). All measurements recorded at an applied ΔT of 20 °C ($T_c = 20$ °C).

voltage produced by thermocell devices, and also increase the overall power output.

Given that for in-series thermocells the overall current output cannot exceed the current of a single thermocell, connection electrically in-parallel is also useful.⁴ This serves to reduce the internal resistance, and potentially double the overall current output (once again potentially doubling the overall P_{max} output). This was evaluated for the $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ thermocells; Fig. 9(c) displays the power curve for one individ-



ual $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ thermocell and for two connected electrically in-parallel; the overall current increased by a factor of 1.8, thus boosting the overall P_{max} by a similar factor.

Towards 'unbreakable' thermocells for thermal energy harvesting

A device was prepared comprising of 6 thermocells (full details in Experimental) in order to further boost the overall power by combining in-series 3 pairs of n-type and p-type thermocells. Following on from the results discussed above, an 'all- FeSO_4 -based' thermocell was prepared containing $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$; we were also able to explore the implications of the 'accidental' mixing of the two types of electrolytes in the device, without risk. This device now employed 12 graphite electrodes, since 12 gold electrodes were not available.

Fig. 10(a) displays the power curves generated for a 2-cell device (one $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and one $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ in-series) and for a 6-cell device (three $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and three $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ in-series; this is shown visually in Fig. 10(a)). As expected, the potential and power essentially tripled. Notably, the absolute

power from these devices are slightly lower than those discussed above, because this larger device used graphite electrodes, whereas gold was used for the investigations above; gold was a better electrocatalyst for the $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ system (as demonstrated by R_{ET} measurements; Fig. S6†).

Next, the implication of a leak resulting in complete electrolyte mixing was explored. Combining $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ and $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ results in a single solution with 0.3 M iron(II) sulphate, 0.3 M iron(III) sulphate, 0.75 M NaHSO_4 and 0.75 M Na_2SO_4 . Overall, this gave an aS_e of $+0.19 \text{ mV K}^{-1}$ ($\Delta T = 20 \text{ K}$, $T_c = 20^\circ\text{C}$); the thermogalvanic characterisation of this electrolyte is further discussed in the ESI (Fig. S8–S10†). Therefore complete mixing throughout the device will result in a still-viable thermoelectrochemically-active electrolyte; however, since all 6 cells are now n-type, they cannot be operated in-series.

Fig. 10(b) displays the power curves generated by 1-cell containing the mixed electrolyte, and the 6-cell device when the electrodes were all connected to make it an electrically in-parallel device; this was achieved simply by placing a sheet of

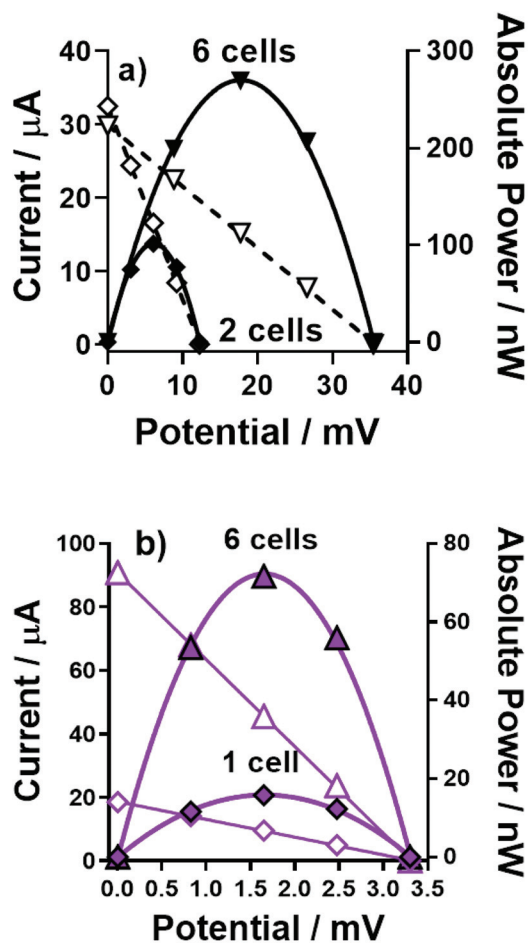


Fig. 10 Showing power curves (filled symbols; solid lines) and I - V data (hollow symbols; dashed lines), as well as associated schematic cartoons, for (a) one pair of $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ – $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ thermocells electrically in-series (black diamonds) and three pairs in-series (black inverted triangles). Similar data is shown in (b) after the two electrolytes have been mixed, showing the data for one mixed electrolyte thermocell (purple diamonds) and six mixed electrolyte thermocells electrically in-parallel (purple triangles). All measurements recorded at an applied ΔT of 20 K ($T_c = 20^\circ\text{C}$).



Principles of Green Chemistry (GC) & Green Engineering (GE) (adapted from ref. 53 and 54)	HCl-acidified FeClO_4 and $\text{K}_3/[\text{NH}_4]_4[\text{Fe}(\text{CN})_6]$ in-series thermocell (exemplified by ref. 16)	All- FeSO_4 in-series thermocell (this work)
– Minimise material diversity (GE 9)	✗ 7 elements/ molecules; complexity lost on mixing ($\text{Fe}^{2+/3+}$, H^+ , K^+ , $(\text{NH}_4)^+$, $[\text{ClO}_4]^-$, Cl^- , $[\text{Fe}(\text{CN})_6]^{3-/4-}$)	✓ 4 elements/ molecules; complexity retained on mixing ($\text{Fe}^{2+/3+}$, Na^+ , $[\text{HSO}_4]^-$, $[\text{SO}_4]^{2-}$)
– Conserve complexity (GE 6)		
– Designing safe chemicals (GC 4)	✗ Individually safe, hazardous if mixed;	✓ Safe, both individually and mixed
– Safer chemistry for accident prevention (GC 12)	$[\text{Fe}(\text{CN})_6]^{4-}$ harmful to aquatic life (long lasting effects)	
– Inputs/outputs inherently non-hazardous (GE 1)		
– Design for degradation (GC 10)	✓ Biodegradable or already elemental	✓ Biodegradable or already elemental
– Durability vs. Immortality (GE 7)		
– Design for commercial ‘afterlife’ (GE 11)	✗ Mixing cannot be reversed; results in ‘end-of-life’	✓ Mixing enables ‘second life’ of thermocell
	✗ Insoluble and toxic waste generated if mixed	✓ ‘Second life’ can prevent waste
– Waste prevention (GC 1)		
– Waste prevention instead of treatment (GE 2)		
– Design energy efficiency (GC 6)	✓ $S_e = 1.7 + 1.3 \text{ mV K}^{-1}$	✗ $\alpha S_e = 0.5 + 0.3 \text{ mV K}^{-1}$
– Maximise efficiency (GE 4)	$= 3.0 \text{ mV K}^{-1}$	$= 0.8 \text{ mV K}^{-1}$
Total number of rows thermocell is superior in	2	5

In this study it was demonstrated how an inversion of the Seebeck coefficient (S_e) could be achieved in an all-iron-sulphate thermogalvanic system, to achieve the equivalent of both the n-type and p-type systems common to thermoelectric devices. While the S_e of aqueous iron(II/II) sulphate solutions ($S_e = ca. +0.3 \text{ mV K}^{-1}$) and their acidified analogues ($S_e = ca. +0.9 \text{ mV K}^{-1}$) have been previously reported, we report here that much milder acidification can be achieved with NaHSO_4 .

while still almost doubling the S_e to $+0.57 \text{ mV K}^{-1}$. Conversely, it was demonstrated for the first time that Na_2SO_4 can be added to invert the entropic direction of the thermogalvanic process in the p-type direction, with a S_e of -0.4 mV K^{-1} easily achieved. It was further demonstrated how these two novel systems can be combined electrically in-series, to additively boost the S_e of the combined device, and thus increase overall thermogalvanic power output. For example, combining 2-cells in-series generated 97% of the sum of the power of the individual cells; moving from 2-cells to 6-cells essentially tripled the power output.

These all-iron-sulphate thermogalvanic systems are less powerful than the comparatively more investigated $\text{Fe}^{2+/3+}$ and $[\text{Fe}(\text{CN})_6]^{3-/4-}$ thermocells, as demonstrated clearly by their combined Seebeck coefficients being *ca.* 25% of the 'state-of-the-art' value¹⁴ (0.8 vs. 3.2 mV K^{-1} , respectively). However, research into the aforementioned systems has not focussed upon introducing any safer thermocells or combinations to reduce the potential hazards; existing reports instead contain an inherent risk of hydrogen cyanide gas release. It was clearly demonstrated here that mixing of the all-iron-sulphate thermogalvanic electrolytes could occur safely, and even retain functionality as a mixed electrolyte system ($S_e = +0.19 \text{ mV K}^{-1}$) thus demonstrating a potential 'second life' application of this system.

The novel iron(II/III) sulphate systems presented here are proposed as more benign alternatives to the conventional $\text{Fe}^{2+/3+}$ and $[\text{Fe}(\text{CN})_6]^{3-/4-}$ thermocells, which are potentially lethal if combined. The thermoelectrochemically quantified ΔS_{rc} values for the thermocells also allowed a detailed and quantitative analysis of the speciation. This could be employed in the future to probe other concentration-dependent transitions, and potentially those triggered by pH, solvent, *etc.* This study also highlights the need to carefully consider the 'what if' aspects of thermocells, including their potential for mixing, and their 'end-of-life' and even 'second life' possibilities.

Conflicts of interest

The authors have no conflicts of interest to declare.

Acknowledgements

M. A. B. acknowledges the EPSRC for funding (Standard Research Studentship (DTP), EP/N509498/1).

References

- 1 T. I. Quickenden and Y. Mua, *J. Electrochem. Soc.*, 1995, **142**, 3985–3994.
- 2 Fitriani, R. Ovik, B. D. Long, M. C. Barma, M. Riaz, M. F. M. Sabri, S. M. Said and R. Saidur, *Renewable Sustainable Energy Rev.*, 2016, **64**, 635–659.
- 3 L. B. Kong, T. Li, H. H. Hng, F. Boey, T. Zhang and S. Li, *Waste Energy Harvesting*, 2014, vol. 24.
- 4 M. Al Maimani, J. J. Black and L. Aldous, *Electrochem. Commun.*, 2016, **72**, 181–185.
- 5 A. Montecucco, J. Siviter and A. R. Knox, *Appl. Energy*, 2014, **123**, 47–54.
- 6 C. B. Vining, *Nat. Mater.*, 2009, **8**, 83–85.
- 7 Endangered Elements, <https://www.acs.org/content/acs/en/greenchemistry/research-innovation/endangered-elements.html>.
- 8 G. Tan, L. D. Zhao and M. G. Kanatzidis, *Chem. Rev.*, 2016, **116**, 12123–12149.
- 9 J. Wu, J. J. Black and L. Aldous, *Electrochim. Acta*, 2017, **225**, 482–492.
- 10 B. Burrows, *J. Electrochem. Soc.*, 1976, **123**, 154–159.
- 11 T. I. Quickenden and C. F. Vernon, *Sol. Energy*, 1986, **36**, 63–72.
- 12 S. G. Bratsch and J. Phys., *Chem. Ref. Data*, 1989, **18**, 1–21.
- 13 J. J. Black, T. Murphy, R. Atkin, A. Dolan and L. Aldous, *Phys. Chem. Chem. Phys.*, 2016, **18**, 20768–20777.
- 14 J. H. Kim, J. H. Lee, R. R. Palem, M. S. Suh, H. H. Lee and T. J. Kang, *Sci. Rep.*, 2019, **9**, 8706.
- 15 L. Zhang, T. Kim, N. Li, T. J. Kang, J. Chen, J. M. Pringle, M. Zhang, A. H. Kazim, S. Fang, C. Haines, D. Al-Masri, B. A. Cola, J. M. Razal, J. Di, S. Beirne, D. R. MacFarlane, A. Gonzalez-Martin, S. Mathew, Y. H. Kim, G. Wallace and R. H. Baughman, *Adv. Mater.*, 2017, **29**, 1605652.
- 16 K. Kim, S. Hwang and H. Lee, *Electrochim. Acta*, 2020, **335**, 135651.
- 17 P. Yang, K. Liu, Q. Chen, X. Mo, Y. Zhou, S. Li, G. Feng and J. Zhou, *Angew. Chem., Int. Ed.*, 2016, **55**, 12050–12053.
- 18 H. Jia, Z. Ju, X. Tao, X. Yao and Y. Wang, *Langmuir*, 2017, **33**, 7600–7605.
- 19 Y. Liang, J. K. H. Hui, T. Yamada and N. Kimizuka, *ChemSusChem*, 2019, **12**, 4014–4020.
- 20 L. Aldous, J. J. Black, M. C. Elias, B. Gélinas and D. Rochefort, *Phys. Chem. Chem. Phys.*, 2017, **19**, 24255–24263.
- 21 J. Duan, B. Yu, K. Liu, J. Li, P. Yang, W. Xie, G. Xue, R. Liu, H. Wang and J. Zhou, *Nano Energy*, 2019, **57**, 473–479.
- 22 M. A. Buckingham, F. Marken and L. Aldous, *Sustainable Energy Fuels*, 2018, **2**, 2717–2726.
- 23 M. A. Buckingham, S. Hammoud, H. Li, C. J. Beale, J. T. Sengel and L. Aldous, *Sustainable Energy Fuels*, 2020, **4**, 3388–3399.
- 24 C. A. P. Arellano and S. S. Martinez, *Sol. Energy Mater. Sol. Cells*, 2010, **94**, 327–332.
- 25 S. Asperger, *Trans. Faraday Soc.*, 1952, **48**, 617–624.
- 26 S. Asperger, I. Murati and D. Pavlovic, *J. Chem. Soc.*, 1953, 730–736.
- 27 J. M. Kruse and L. E. Thibault, *Anal. Chem.*, 1973, **45**, 2260–2261.
- 28 P. L. Domingo, B. Garcia and J. M. Leal, *Can. J. Chem.*, 1990, **68**, 228–235.



- 29 H. Basset and A. S. Corbet, *J. Chem. Soc. Trans.*, 1924, 1358–1366.
- 30 A. S. Brar, H. S. Sandhu and H. S. Sandhu, *Thermochim. Acta*, 1980, **41**, 253–256.
- 31 A. S. Brar, H. S. Sandhu and S. S. Sandhu, *J. Therm. Anal.*, 1983, **26**, 7–15.
- 32 A. S. Brar, H. Singh, S. Brar and B. S. Randhawa, *J. Therm. Anal.*, 1981, **21**, 77–88.
- 33 J. I. Kunrath, C. S. Müller and E. Frank, *J. Therm. Anal.*, 1978, **14**, 253–264.
- 34 M. Ruiz-Bermejo, C. Rogero, C. Menor-Salván, S. Osuna-Esteban, J. Á. Martín-Gago and S. Veintemillas-Verdaguer, *Chem. Biodivers.*, 2009, **6**, 1309–1322.
- 35 A. C. L. Câmara and B. Soto-Blanco, Cyanide poisoning in animals and humans, *Cyanide: Occurrence, Characteristics and Applications*, ed. B. Soto-Blanco, Nova Science Publishers, Inc., 2013, pp. 23–46.
- 36 F. Musshoff, K. M. Kirschbaum and B. Madea, *Forensic Sci. Int.*, 2011, **204**, e4–e7.
- 37 A. H. Hall and B. H. Rumack, *Ann. Emerg. Med.*, 1986, **15**, 1067–1074.
- 38 H. A. H. Alzahrani, M. A. Buckingham, F. Marken and L. Aldous, *Electrochem. Commun.*, 2019, **102**, 41–45.
- 39 Sigma-Aldrich, Potassium ferricyanide(III) – SDS, <https://www.sigmaaldrich.com/MSDS/MSDS/DisplayMSDSPage.do?country=GB&language=en&productNumber=702587&brand=SIGALD&PageToGoToURL=https%3A%2F%2Fwww.sigmaaldrich.com%2Fcatalog%2Fsearch%3Fterm%3DPotassium%2Bferricyanide%26interface%3DAll%26N%3D0%26mode%3Dpar>, (accessed 18 May 2020).
- 40 Sigma-Aldrich, Potassium hexacyanoferrate(II) trihydrate – SDS, <https://www.sigmaaldrich.com/MSDS/MSDS/DisplayMSDSPage.do?country=GB&language=en&productNumber=P3289&brand=SIGALD&PageToGoToURL=https%3A%2F%2Fwww.sigmaaldrich.com%2Fcatalog%2Fsearch%3Fterm%3DPotassium%2Bferricyanide%26interface%3DAll%26N%3D0%26mode%3Dpar>, (accessed 18 May 2020).
- 41 Hydrogen Cyanide, https://www.cdc.gov/niosh/ershdb/emergencyresponsecard_29750038.html, (accessed 18 May 2020).
- 42 M. A. Buckingham and L. Aldous, *J. Electroanal. Chem.*, 2020, DOI: 10.1016/j.jelechem.2020.114280.
- 43 J. T. Hupp and M. J. Weaver, *Inorg. Chem.*, 1984, **23**, 3639–3644.
- 44 L. L. Trent, R. S. Hestand and C. C. Carter, *J. Aquat. Plant Manage.*, 1978, **16**, 40–43.
- 45 N. N. Greenwood and A. Earnshaw, *Chemistry of the Elements*, Pergamon Press Ltd., Leeds, 1984.
- 46 R. J. Lemire, U. Berner, C. Musikas, D. A. Palmer, P. Taylor and O. Tochiyama, *Chemical thermodynamics of iron Part 1, OECD*, 2013, vol. 13a.
- 47 J. Majzlan and S. C. B. Myneni, *Environ. Sci. Technol.*, 2005, **39**, 188–194.
- 48 E. H. B. Anari, M. Romano, W. X. Teh, J. J. Black, E. Jiang, J. Chen, T. Q. To, J. Panchompoo and L. Aldous, *Chem. Commun.*, 2016, **52**, 745–748.
- 49 F. J. Millero, W. Yao and J. Aicher, *Mar. Chem.*, 1995, **50**, 21–39.
- 50 J. T. Hupp and M. J. Weaver, *J. Phys. Chem.*, 1984, **88**, 1860–1864.
- 51 D. H. Ripin and D. A. Evans, *pKa's of Inorganic and Oxo-Acids*, 2005, http://evans.rc.fas.harvard.edu/pdf/evans_pKa_table.pdf (accessed 2020).
- 52 N. Jiao and S. Evans, *Procedia CIRP*, 2016, **40**, 250–255.
- 53 P. Anastas and J. Warner, *Green Chemistry: Theory and Practice*, Oxford University Press, Oxford [England], 2000.
- 54 P. T. Anastas and J. B. Zimmerman, *Environ. Sci. Technol.*, 2003, **37**, 94A–101A.

