

Cite this: *Mater. Horiz.*, 2020,
7, 2951Received 25th June 2020,
Accepted 25th August 2020

DOI: 10.1039/d0mh01044h

rsc.li/materials-horizons

Charge transfer excitons in a donor–acceptor
amphidynamic crystal: the role of dipole
orientational order†Joshua W. R. Macdonald,^{*a} Giacomo Piana,^b Massimiliano Comin,^{id c}
Elizabeth von Hauff,^{id d} Gabriele Kociok-Köhn,^{id e} Chris Bowen,^f
Pavlos Lagoudakis,^{bg} Gabriele D'Avino^{id c} and Enrico Da Como^{id *a}

Large amplitude motions in molecular solids are responsible for anomalous electrical characteristics in amphidynamic crystals. We study the effect of orientational dipolar disorder on charge transfer excitons (CTEs) in a donor–acceptor amphidynamic co-crystal of perylene–tetrabromophthalic anhydride (–TBPA). This co-crystal offers long range positional order of alternating donor and acceptor molecular entities arranged in stacks. Further it has a phase transition at 250 K due to progressive freezing of the dipolar orientational motion in the TBPA permanent dipole. The optical absorption band and photoluminescence at the semiconductor gap consists of at least three energetically separated CTE resonances that cover a spectral range of more than 400 meV. As the temperature is lowered below the phase transition the CTE band remains broad, but shows a shift of ~150 meV to higher energy. On the basis of optical reflectivity, photoluminescence, and model calculations we interpret the room temperature CTE band as a collection of resonances in which at least one the nearest neighbour dipoles to the CTE is flipped from their lowest energy configuration. This first comprehensive optical investigation on an amphidynamic co-crystal demonstrates the importance of understanding the role of permanent dipoles in the CTE photophysics of organic semiconductors.

New concepts

In donor–acceptor molecular systems the fundamental optical excitations are charge transfer excitons (CTEs). These excitons enter directly into the operation of many optoelectronic devices based on organic semiconductors, for example they determine the power conversion efficiency of solar cells or the light emission colour of light emitting diodes. The common understanding about CTEs is that the HOMO of donors and LUMO of acceptors largely determine the energy of the CTE optical transitions. Commonly those exhibit broad optical signatures in absorption and emission due to structural disorder and molecular vibrations. In this paper we demonstrate that even in a perfectly ordered material system such as a charge transfer single crystal, the CTE absorption and photoluminescence emission is remarkably broad in energy. By using a novel class of materials such as amphidynamic crystals we show how orientational dipolar disorder results in the generation of a series of CTE resonances, all contributing to the observed broad band. By probing the resonances at different temperatures we show how freezing of dynamical disorder still results in residual CTE transition splitting due to electrostatic interactions. Our work provides novel insights into the energetics and photoluminescence efficiency of CTEs and how these crucial parameters could be tuned by a judicious choice of crystalline arrangements of permanent dipoles.

Introduction

When an electron and a hole straddle over at least two molecules and interact by their mutual Coulomb potential, the most fundamental particle in organic optoelectronics is formed; the

charge transfer exciton (CTE). Such excitations dominate the operation of organic light emitting diodes and solar cells,^{1–3} yet understanding of their underlying physics remains far from being complete. While the role of CTE in electroluminescence is crucially linked to spin dynamics and recombination.^{4,5} With regard to the photovoltaic effect there is continued debate on the mechanism by which geminate electrons and holes that

^a Centre for Photonics and Photonic Materials (CPPM) and Department of Physics, University of Bath, Claverton Down, Bath BA2 7AY, UK. E-mail: e.da.como@bath.ac.uk, j.w.r.macdonald@bath.ac.uk^b Physics and Astronomy, University of Southampton, University Road, Southampton SO17 1BJ, UK^c Institut Néel CNRS and Université Grenoble Alpes, F-38042 Grenoble, France^d Department of Physics and Astronomy, Vrije Universiteit, de Boelelaan 1081, 1081 HV Amsterdam, The Netherlands^e Material and Chemical Characterization Facility (MC²), University of Bath, Claverton Down, Bath BA2 7AY, UK^f Department of Mechanical Engineering, University of Bath, Claverton Down, Bath BA2 7AY, UK^g Skolkovo Institute of Science and Technology (Skoltech), Skolkovo, Moscow 121205, Russia

† Electronic supplementary information (ESI) available. CCDC 1995103 and 1995104. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0mh01044h



constitute the CTE are able to spatially separate and escape the coulombic well.^{6–8} There are a number of factors influencing CTE dissociation in its constituent charged particles which include: electronic delocalization,^{8–11} interface dipole layers,¹² localized dipoles,¹³ molecular doping,¹⁴ entropy,¹⁵ and disorder in the local density of states.^{16,17}

In addition, the energy of the CTE and its luminescence efficiency are linked to a critically important device parameter; the cell open-circuit-voltage.¹⁸ A microscopic understanding of the electrostatic interactions governing the CTE energetics has yet to be addressed in detail, in part due to the chemical diversity of organic semiconductors resulting in a multitude of heterojunctions which can form. These can range from planar two-dimensional interfaces^{19,20} to molecularly dispersed blends of a donor and an acceptor²¹ which, while being device relevant, are often microscopically ill defined.¹¹ Furthermore the recent interest in electrostatic phenomena in organic semiconductors²² calls for studies on model structurally defined systems where the effect of dipoles and quadrupoles²³ can be controlled.

Here we want to focus on molecularly dispersed systems and clearly the most defined organic material for molecularly dispersed donor–acceptor junctions is a charge transfer co-crystal.^{24,25} In such solids the electrostatic interactions between two molecules of different electron affinity generate an alternating structure of donor and acceptor molecular entities, thereby building a bulk crystal. It has been firmly established that the photophysics of such co-crystals is dominated by CTEs,^{26,27} but the role of electronic delocalization, disorder and in particular localized dipoles on the CTE characteristics has remained largely unexplored.²⁷ An opportunity to study the role of localized molecular dipoles has been recently provided by the work of Harada *et al.*²⁸ Their co-crystal between the donor, perylene, and the acceptor, tetrabromophthalic anhydride (TBPA), is an ideal system to study dipolar effects on CTEs since the acceptor TBPA molecule has a strong permanent dipole, estimated to be 4.5 Debye.²⁸ Interestingly, the TBPA molecules, and thus the dipoles, exhibit a dynamic reorientation by 180° above 250 K, while below this temperature they start to localize in a fixed crystallographic orientation.

Perylene–TBPA can be thus considered an amphidynamic crystal,^{29–31} *i.e.* a molecular material displaying rapid and large-amplitude molecular motions in the solid state, resulting in unique electrical properties due to the combined effect of electronic structure and dynamic motion. In fact, the decrease in the frequency of TBPA dynamic reorientation leads to a phase transition at 250 K, where the room temperature phase of the co-crystal, that has a relative permittivity of $\epsilon = 15$, transforms into a low temperature phase (LTP), and is claimed to be anti-ferroelectric.²⁸ In the low temperature anti-ferroelectric phase, TBPA dipoles are fixed and aligned antiparallel within the unit cell. The phase transition leads to a collapse of the relative permittivity to $\epsilon = 5$ (ref. 28). Thus perylene:TBPA is not only an interesting solid state molecular machine that can be controlled by the application of electric fields, but also a model material system to study the influence of large changes on the dielectric function on the CTE optical properties without modification of the chemical structure.

In this article, we report on the optical properties of perylene–TBPA single crystals as a function of temperature across the phase transition. We show that a broad CTE absorption band, > 400 meV, includes several resonances whose energy positions and intensities are sensitive to temperature. The modelling of the optical absorption in the presence of thermal orientational disorder provides an immediate explanation of the HTP broad-band absorption and its features as a direct consequence of the accessible microscopic configurations of TBPA molecules with varying orientations. We also report on the PL which maintains the broad features seen in absorption, but with an increasing intensity of its high energy resonances as the temperature is lowered. The crucial role of dipole disorder on CTE energetics and photophysics is discussed in detail, outlining important implications for next generation materials.

Results

Structure of perylene–TBPA

Fig. 1 shows the crystal structure and unit cell of perylene–TBPA in both its high temperature phase (HTP, Fig. 1a) and low temperature phase (LTP, Fig. 1b). The system is a 1 : 1 co-crystal of perylene and TBPA as donor and acceptor, respectively, which are alternately stacked in the unit cell. Donors and acceptors alternate at equal distances and therefore the stack is classified as regular, in contrast to dimerized. In the HTP, the TBPA molecule is seen to reorient 180° in its molecular plane, as indicated by the curved arrows in Fig. 1a. This rotation occurs about a centre of inversion of the unit cell and analysis of the occupation probability from the X-ray experiment shows that the two orientations have the same probability. Conversely, in the LTP the unit cell almost doubles in volume (ESI,† Table S2) and TBPA takes up two opposing orientations in two inequivalent sites of the unit cell. Since TBPA is not a centrosymmetric molecule, the two acceptor molecules per unit cell are oriented with opposite permanent dipoles.

A more quantitative examination of the differences between the two phases is shown in Table 1, with a comparison of



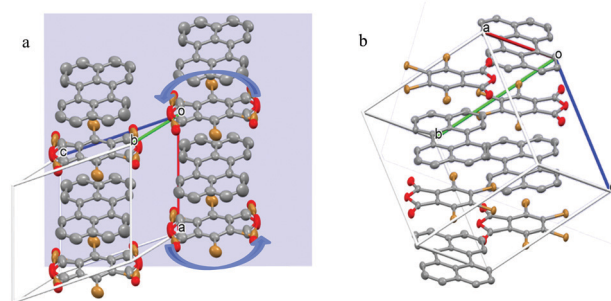


Fig. 1 Unit cell of perylene–TBPA in (a) HTP at 290 K and (b) LTP at 150 K. Curved arrows in (a) are included to highlight the TBPA dynamic reorientation. In TBPA the coloured atoms indicate oxygen (red) and bromine (brown). In the HTP of (a) the bromine and oxygen atoms appear superimposed because of the dynamical reorientation. The background plane in (a) represents the crystal face used for optical reflectivity measurements. Unit cell parameters are reported in the ESI.†



Mater. Horiz., 2020, 7, 2951–2958 | 2953



intra-stack CT transitions present a non-negligible ($\sim 10\%$) absorption cross section polarized perpendicular to the stack, as further discussed in the ESI.[†] This, together with the uncertainty associated with the comparison of reflectivity intensities for different polarizations, may rationalize the similar absorption intensities obtained for two light polarization in Fig. 3.

CTE degrees of freedom are described on a minimal basis corresponding to the three lowest-energy charge configurations shown in Fig. 5a, and accounting for intermolecular hopping integrals mixing the basis states. The energies of the CT electronic configurations, $|1\rangle$ and $|2\rangle$, includes the excitonic electron-hole interaction. Most importantly, these energies are also affected by the electrostatic landscape generated by the molecules surrounding the region where CT takes place. Electrostatic energies are assessed with a simple model where TBPA molecules are described as extended dipoles, which allows calculation of the electrostatic potential at molecular

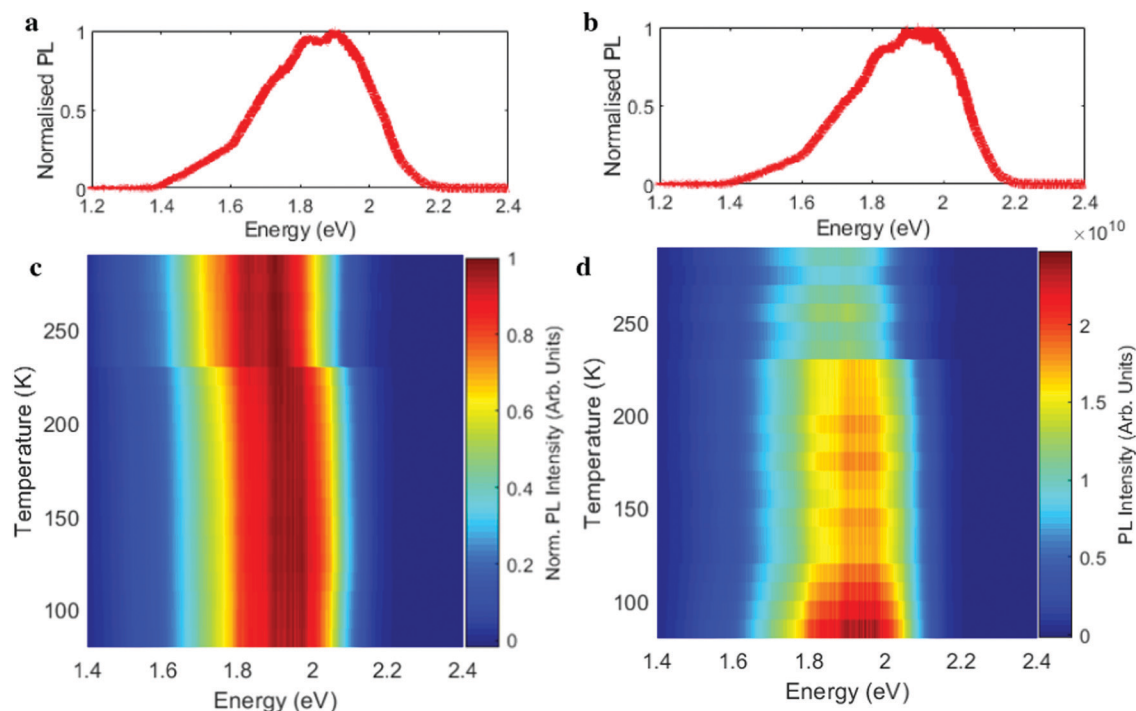


Fig. 4 Normalized photoluminescence spectrum at (a) room temperature, (b) 150 K, (c) normalized as a function of temperature, and (d) as a function of temperature without intensity normalization. Excitation at 2.95 eV.

sites retaining the specificities of the crystal packing in the two phases. The model is described in detail in the ESI†

The LTP crystal structure presents two symmetry inequivalent perylene located on inversion sites. This asymmetry determines different electrostatic potentials, generated by the dipoles of TBPA molecules, at the two D sites, leading to two CT configurations, $|1\rangle$ and $|2\rangle$, with energies differing by ~ 0.3 eV (see inset in Fig. 5b). The absorption spectrum in Fig. 5b is hence characterized by two CT transitions of almost equal oscillator strength, corresponding to an electron transfer from each of the two asymmetric perylenes to the central TBPA. In this calculation we have considered the LTP crystal as a perfect crystalline solid at $T = 0$ K, *i.e.* without the possibility of thermal excitations causing the reorientation of any TBPA. The two CTE resonances shown in Fig. 5b are thus the result of the different crystal fields experienced by the two inequivalent perylene, due to the locked dipole of the neighbouring TBPA molecules, with a smaller contribution from intermolecular CT interactions. The inset gives a visual rendering of the two effects.

The structure of the HTP contains only one donor–acceptor pair per unit cell, thus in contrast to the LTP, all perylenes are equivalent. It is, however, characterized by the disorder of TBPA that can be found in two opposite orientations (*cf.* Fig. 1a). To allow for a microscopic assessment of the dipolar field, we had to resolve the uncertainty in the structure associated with the fractional population of TBPA orientations. We did this by considering that the LTP is the most energetically stable configuration, hence building a hypothetical HTP crystal supercell with TBPA relative orientations analogous to those in the LTP. This hypothetical zero-temperature (disorder-free) HTP

crystal structure can be superimposed to the LT one, revealing that, except for the thermal lattice expansion and for small changes in molecular orientations, the two structures are almost identical. We notice that the dipoles of neighbouring TBPA molecules are parallel along the axis *b* and anti-parallel along *a* and *c* (Fig. 5e and f). The resulting nearest-neighbour dipolar interactions are all attractive and stabilize this configuration.

Fig. 5c shows the absorption spectrum calculated for the disorder-free HTP structure. The two perylenes of the trimer are only slightly inequivalent, leading to two CT configurations that differ only by ~ 50 meV (see inset in Fig. 5c). In this case, the large majority of the absorption intensity goes to the lowest-energy dipole-allowed excitation, which corresponds to an approximately symmetric electron transfer from the two Ds to the A. The absorption spectrum of this hypothetical disorder-free HTP is hence characterized by a single absorption peak, at an energy in between the two bands calculated for the LTP (*cf.* Fig. 5b and c).

Having examined the two hypothetical cases above, which do not include disorder in dipole orientations, we turn now on the effect of thermally accessible microscopic configurations, featuring TBPA dipoles that are flipped with respect to the defect-free HTP structure. To achieve this we performed a stochastic sampling of disorder based on our electrostatic model, ultimately enabling the calculation of the absorption spectra at finite temperature, see ESI† for full details on the sampling. The calculated absorption spectrum of the HTP is shown in Fig. 5d and presents a remarkably broad CTE band, extending between 1.6 and 2.1 eV. The band is composed of



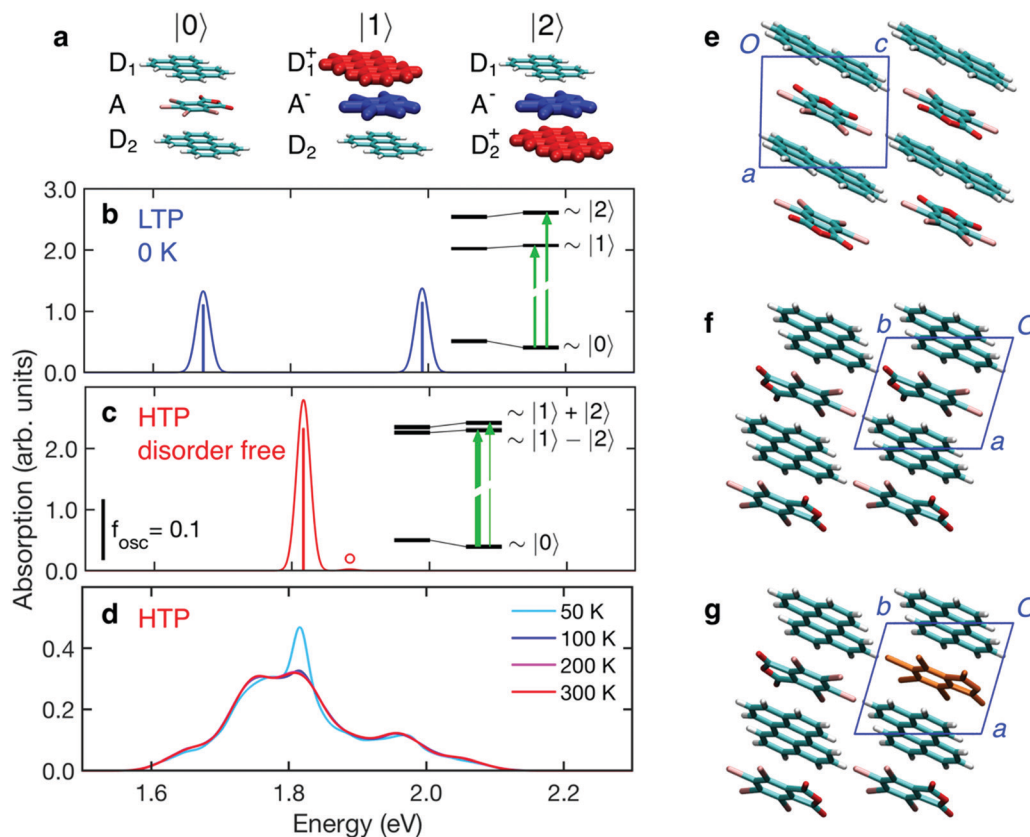


Fig. 5 Theoretical analysis of the optical absorption of perylene-TBPA. (a) Sketch of the basis states of the three-state model used to interpret optical spectra polarized along the stack axis. Absorption spectra of the LTP (at 0 K) (b), of the HTP both in its hypothetical disorder-free structure (c) and at finite temperature (d). The height of vertical bars in (b) and (c) correspond to the calculated oscillator strength (f_{osc} , see scale in b); insets illustrate the energy levels of basis states (left) and eigenstates (right), and the transitions between the latter as arrows. (e and f) Rendering of the disorder-free HTP crystal structure that closely resembles the molecular arrangement in the LTP. (g) Illustration of an orientational defect in the HTP structure, corresponding to a TBPA molecule (in orange) that has been flipped with respect to the disorder-free structure.

several peaks and shows a weak dependence on temperature in the relevant temperature window (200–300 K).

The good agreement between the experimental (Fig. 3b) and calculated spectra allows us to ascribe the broad absorption feature to thermal dipolar disorder in the HTP. A closer examination of the calculated and experimental spectra reveals that these are characterized by some partially resolved peaks. Our calculations allow us to assign the most intense band to the absorption of the disorder-free structure (*cf.* Fig. 5c and d), while other peaks can be assigned to thermally-accessible configurations in which TBPA molecules are flipped with respect to the minimum-energy structure, *i.e.* “orientational defects”. Fig. 5g shows an example of a single TBPA molecule being rotationally misaligned to its lowest energy configuration. We emphasize that the occurrence of partly-resolved peaks, instead of in a featureless broadening of the main peak, is a specific signature of the discrete nature of dipolar disorder in the HTP, where only two specific molecular orientations of TBPA are possible. A close inspection of the characteristic spectroscopic signature of orientational defects reveals that nearest neighbour dipoles along the *a* and *b* crystallographic axis play a major role in contributing to resonances which are 50–150 meV either side of the central 1.8 eV peak. Fig. S3 in ESI†

shows a decomposition of the broad spectrum of Fig. 5d, which pinpoints the single TBPA misoriented molecules responsible for each peak.

The clear disagreement between the experimental and calculated absorption spectra of the LPT suggests that residual (quenched) disorder persists below the transition temperature, as also evinced from a careful analysis of X-ray.²⁸ The presence of quenched disorder in the LTP is also consistent with the large activation energy ($56 \text{ kJ mol}^{-1} = 580 \text{ meV}$) estimated from dielectric measurements,¹⁹ which may be associated with energy barriers for TBPA flipping, and with the evidence for a significant relaxation dynamics in the LTP, at least in the proximity of the transition.

Finally, we note the reduced PL intensity in the HTP of Fig. 4b is consistent with having non-radiative channels for CTE recombination. As the rotational motion of TBPA decreases and then ceases with reducing temperature, the structure of Fig. 1b should promote recombination with a decreased number of non-radiative channels. In addition, our estimations of transfer integrals in the two structures show that in the LTP the wave function overlap between perylene and TBPA is higher, thereby promoting radiative recombination. From our experimental data, we see a further increase in PL below $\sim 150 \text{ K}$, which we



believe to correspond with the cessation of the TBPA dynamic motion. This cessation of motion could also explain the CTE peaks of Fig. 3 not shifting further below 150 K and the change in angles presented in Table 1.

Discussion and conclusions

The implications of our studies for the CTE photophysics in systems relevant for organic photovoltaics is immediate. Dipolar interactions at the molecular scale can have dramatic effects on the energy of CTE states. Relative orientations between the dipoles in close proximity to the donor acceptor molecules involved in the CTE determine its energy with shifts up to ~ 200 meV. Thus, the CTEs cannot be considered as independent quasiparticles involving only the donor and acceptor, but rather an electron and hole pair interacting with the nearest neighbour permanent dipoles in a complex electrostatic energy landscape. Considering the fundamental link between the CTE energy and the open circuit voltage of organic solar cells, local electrostatics arising from permanent dipoles appears to be a tantalizing opportunity to tune and control the overall efficiency of solar cells. Further work should focus on the supramolecular design of dipolar orientations capable of maximizing high energy CTE resonances with high oscillator strengths and the expenses of low energy non-radiative ones.

In conclusion, we have grown perylene-TBPA amphidynamic co-crystals which undergo an order-disorder phase transition with the purpose of studying the effects of dipolar order on the CTEs. We have found that the presence of the dipolar TBPA molecule and its dynamic reorientation in its crystallographic site leads to the splitting of the CTE resonance due to their intertwined electrostatics. As the temperature was lowered below the phase transition and the degree of dipole reorientation reduced, the CTE band shifted to higher energy, but remained intrinsically broad. On the basis of an electrostatic excitonic model we have attributed the broad CTE band to many different resonances arising from misaligned dipoles from their lowest energy configuration. Lastly, PL experiments revealed that the different CTE resonances emit independently over a broad spectrum and with an increased radiative contribution once dipoles cease to reorient. These findings are of importance for the understanding and subsequent design of novel organic and hybrid semiconducting materials, in particular for future organic photovoltaic applications based on supramolecular amphidynamic systems.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

JM and EDC acknowledge EPSRC and the CDT in New and Sustainable Photovoltaics (project EP/L01551X/1) for funding and support. GP and PL thank the EPSRC for funding (project

EP/M025330/1). EDC acknowledges support from the Royal Society for a Wolfson Lab Refurbishment grant (WL120030).

References

- 1 K. Vandewal, K. Tvingstedt, A. Gadisa, O. Inganäs and J. V. Manca, *Nat. Mater.*, 2009, **8**, 904–909.
- 2 V. Coropceanu, X. K. Chen, T. H. Wang, Z. L. Zheng and J. L. Bredas, *Nat. Rev. Mater.*, 2019, **4**, 689–707.
- 3 J. Lee, K. Vandewal, S. R. Yost, M. E. Bahlke, L. Goris, M. A. Baldo, J. V. Manca and T. Van Voorhis, *J. Am. Chem. Soc.*, 2010, **132**, 11878–11880.
- 4 M. Reufer, M. J. Walter, P. G. Lagoudakis, B. Hummel, J. S. Kolb, H. G. Roskos, U. Scherf and J. M. Lupton, *Nat. Mater.*, 2005, **4**, 340–346.
- 5 T. Basel, D. L. Sun, S. Baniya, R. McLaughlin, H. Choi, O. Kwon and Z. V. Vardeny, *Adv. Electron. Mater.*, 2016, **2**, 9.
- 6 H. Bässler and A. Kohler, *Phys. Chem. Chem. Phys.*, 2015, **17**, 28451–28462.
- 7 K. Vandewal, S. Albrecht, E. T. Hoke, K. R. Graham, J. Widmer, J. D. Douglas, M. Schubert, W. R. Mateker, J. T. Bloking, G. F. Burkhard, A. Sellinger, J. M. J. Frechet, A. Amassian, M. K. Riede, M. D. McGehee, D. Neher and A. Salleo, *Nat. Mater.*, 2014, **13**, 63–68.
- 8 G. D'Avino, L. Muccioli, Y. Olivier and D. Beljonne, *J. Phys. Chem. Lett.*, 2016, **7**, 536–540.
- 9 M. Hallermann, I. Kriegel, E. Da Como, J. M. Berger, E. von Hauff and J. Feldmann, *Adv. Funct. Mater.*, 2009, **19**, 3662–3668.
- 10 A. A. Bakulin, A. Rao, V. G. Pavelyev, P. H. M. Van Loosdrecht, M. S. Pshenichnikov, D. Niedzialek, J. Cornil, D. Beljonne and R. H. Friend, *Science*, 2012, **335**, 1340–1344.
- 11 D. Fazzi, M. Barbatti and W. Thiel, *J. Phys. Chem. Lett.*, 2017, **8**, 4727–4734.
- 12 V. I. Arkhipov, P. Heremans and H. Bassler, *Appl. Phys. Lett.*, 2003, **82**, 4605–4607.
- 13 B. Carsten, J. M. Szarko, H. J. Son, W. Wang, L. Y. Lu, F. He, B. S. Rolczynski, S. J. Lou, L. X. Chen and L. P. Yu, *J. Am. Chem. Soc.*, 2011, **133**, 20468–20475.
- 14 F. Deschler, E. Da Como, T. Limmer, R. Tautz, T. Godde, M. Bayer, E. von Hauff, S. Yilmaz, S. Allard, U. Scherf and J. Feldmann, *Phys. Rev. Lett.*, 2011, **107**, 127402.
- 15 N. R. Monahan, K. W. Williams, B. Kumar, C. Nuckolls and X. Y. Zhu, *Phys. Rev. Lett.*, 2015, **114**, 5.
- 16 R. A. Street, *Adv. Mater.*, 2016, **28**, 3814–3830.
- 17 K. Tvingstedt, J. Benduhn and K. Vandewal, *Mater. Horiz.*, 2020, **7**(7), 1888–1900.
- 18 D. P. Qian, Z. L. Zheng, H. F. Yao, W. Tress, T. R. Hopper, S. L. Chen, S. S. Li, J. Liu, S. S. Chen, J. B. Zhang, X. K. Liu, B. W. Gao, L. Q. Ouyang, Y. Z. Jin, G. Pozina, I. A. Buyanova, W. M. Chen, O. Inganäs, V. Coropceanu, J. L. Bredas, H. Yan, J. H. Hou, F. L. Zhang, A. A. Bakulin and F. Gao, *Nat. Mater.*, 2018, **17**, 703–709.
- 19 H. Alves, R. M. Pinto and E. S. Macoas, *Nat. Commun.*, 2013, **4**, 7.



- 20 A. E. Jailaubekov, A. P. Willard, J. R. Tritsch, W. L. Chan, N. Sai, R. Gearba, L. G. Kaake, K. J. Williams, K. Leung, P. J. Rossky and X. Y. Zhu, *Nat. Mater.*, 2013, **12**, 66–73.
- 21 V. Belova, P. Beyer, E. Meister, T. Linder, M. U. Halbich, U. Halbich, S. Schmid, T. Zeche, T. Meisel, A. V. Generalov, A. S. Anselmo, R. Scholz, O. Konovalov, A. Gerlach, M. Koch, A. Hinderhofer, A. Opitz, W. Brutting and F. Schreibert, *J. Am. Chem. Soc.*, 2017, **139**, 8474–8486.
- 22 G. D'Avino, L. Muccioli, F. Castet, C. Poelking, D. Andrienko, Z. G. Soos, J. Cornil and D. Beljonne, *J. Phys.: Condens. Matter*, 2016, **28**, 433002.
- 23 M. Schwarze, W. Tress, B. Beyer, F. Gao, R. Scholz, C. Poelking, K. Ortstein, A. A. Günther, D. Kasemann, D. Andrienko and K. Leo, *Science*, 2016, **352**, 1446–1449.
- 24 M. Pope and C. E. Swenberg, *Electronic Processes in Organic Crystals and Polymers*, Oxford University Press, Oxford, 1999.
- 25 K. P. Goetz, D. Vermeulen, M. E. Payne, C. Kloc, L. E. McNeil and O. D. Jurchescu, *J. Mater. Chem. C*, 2014, **2**, 3065–3076.
- 26 R. J. Dillon and C. J. Bardeen, *J. Phys. Chem. A*, 2012, **116**, 5145–5150.
- 27 J. Tsutsumi, H. Matsui, T. Yamada, R. Kumai and T. Hasegawa, *J. Phys. Chem. C*, 2012, **116**, 23957–23964.
- 28 J. Harada, M. Ohtani, Y. Takahashi and T. Inabe, *J. Am. Chem. Soc.*, 2015, **137**, 4477–4486.
- 29 T. A. V. Khuong, J. E. Nunez, C. E. Godinez and M. A. Garcia-Garibay, *Acc. Chem. Res.*, 2006, **39**, 413–422.
- 30 L. Catalano and P. Naumov, *CrystEngComm*, 2018, **20**, 5872–5883.
- 31 H. Chung, D. Dudenko, F. Zhang, G. D'Avino, C. Ruzié, A. Richard, G. Schweicher, J. Cornil, D. Beljonne, Y. Geerts and Y. Diao, *Nat. Commun.*, 2018, **9**, 278.
- 32 T. Rangel, A. Rinn, S. Sharifzadeh, F. H. da Jornada, A. Pick, S. G. Louie, G. Witte, L. Kronik, J. B. Neaton and S. Chatterjee, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 284.
- 33 A. B. Kuzmenko, *Rev. Sci. Instrum.*, 2005, **76**, 083108.
- 34 A. Brillante and M. R. Philpott, *J. Chem. Phys.*, 1980, **72**, 4019–4030.
- 35 D. Haarer, M. R. Philpott and H. Morawitz, *J. Chem. Phys.*, 1975, **63**, 5238–5245.
- 36 G. Weiser and A. Elschner, *J. Phys. Chem. A*, 2009, **113**, 6910–6918.
- 37 A. Painelli and A. Girlando, *J. Chem. Phys.*, 1986, **84**, 5655–5671.

