


Cite this: *Nanoscale*, 2021, **13**, 16509

Functionalized silica nanoplatfrom as a bimodal contrast agent for MRI and optical imaging†

Sarah Garifo,^a Dimitri Stanicki,^a Sébastien Boutry,^b Lionel Larbanoix,^b Indiana Ternad,^a Robert N. Muller^{a,b} and Sophie Laurent^{*,a,b}

The preparation of an efficient bimodal single probe for magnetic resonance (MRI) and optical imaging (OI) is reported. Paramagnetic properties have been obtained by the non-covalent encapsulation of the clinically used Gd³⁺ chelate (*i.e.*, Gd-HP-DO3A) within silica nanoparticles through a water-in-oil micro-emulsion process. To ensure colloidal stability, the surface of the particles was modified by means of treatment using PEG-silane, and further functionalized photochemically using a diazine linker bearing carboxylic functions. Optical properties were obtained by the covalent grafting of a near-infrared emitting probe (NIR) on the resulting surface. The confinement of Gd complexes within the permeable matrix resulted in a significant increase in longitudinal relaxivities (>500% at 20 MHz) in comparison with the relaxivities of free chelate, while the post-functionalization process of PEG with fluorescent compounds appeared promising for the derivatization procedure. Several physico-chemical properties attested to the efficient surface modification and confirmed covalent grafting. Preliminary imaging experiments complete this study and confirm the potential of the presented system for preclinical imaging experiments.

Received 30th July 2021,
Accepted 19th September 2021

DOI: 10.1039/d1nr04972k

rsc.li/nanoscale

Introduction

For several decades, magnetic resonance imaging (MRI) has been used as a reference tool for medical diagnosis by allowing the tridimensional visualization of various organs and tissues noninvasively and with remarkable spatial resolution (at the submillimeter level for the most efficient devices).^{1,2} The intensity of the signal depends on the intrinsic parameters,

namely, the local proton concentration as well as their longitudinal (R_1) and transverse (R_2) relaxation rates. Depending on the environment and their dynamics, the relaxation rates will change according to the nature of the tissue. The specificity of an MRI exam can be increased by injecting a contrast agent (CA), which will act as a nuclear relaxation booster.³ Typically, paramagnetic ions are able to enhance both R_1 and R_2 by catalyzing the return of water protons to the ground state, thus improving the image contrast where the ions are located. It is estimated that up to 40% of clinical MR examinations are performed by using paramagnetic chelates.^{4,5} However, as a consequence of the poor sensitivity of MRI, a high local concentration of contrast agent is needed to achieve visualizable contrast enhancement.⁶ To improve the relaxivity of a paramagnetic substance, a conventional strategy is to increase the molecular weight of the structure to increase the rotational correlation time value (*i.e.*, τ_R).^{7,8} If the initial strategies implied the development of low molecular weight macrocycles that are able to interact with plasma proteins (*e.g.*, albumin) *in vivo*,^{9,10} then current strategies tend towards the design of macromolecular systems resulting either from covalent grafting of a paramagnetic complex onto a polymeric support (*e.g.*, dendrimers),^{6,11–14} or from the noncovalent confinement of the complex within porous and water-permeable supports,^{15–18} (*e.g.*, apoferritin).^{16,17} Among the different developed systems, those resulting from the combination of a paramagnetic substance and inorganic nanoparticles have been extensively studied and have highlighted promising platforms that are

^aGeneral, Organic and Biomedical Chemistry Unit, NMR and Molecular Imaging Laboratory, University of Mons, 19 avenue Maistriau, 7000 Mons, Belgium.

E-mail: sophie.laurent@umons.ac.be; Tel: +32-(0)65-37-35-25

^bCenter for Microscopy and Molecular Imaging (CMMI), 8 rue Adrienne Bolland, 6041 Gosselies, Belgium

†Electronic supplementary information (ESI) available: Fig. S1. Additional TEM images and histograms of empty SiO₂-NPs through network formation. Fig. S2: Stability measurements of PEG-coated SiO₂-NPs by DLS. Fig. S3: Thermogravimetric curve of empty PEG-coated SiO₂-NPs systems. Fig. S4: Surface modification: FTIR spectra of SiO₂-NPs, PEG-coated SiO₂-NPs and functionalized PEG SiO₂-NPs. Eqn (S1)–(S4). Number of Gd³⁺ complexes embedded inside silica NPs. Table S1: Number of entrapped complexes inside SiO₂-Gd-NPs. Fig. S5: Stability measurements of functionalized PEG-coated SiO₂-Gd-NPs by DLS. Fig. S6: NIR luminescent properties of the multimodal platform: spectroscopy and imaging. Fig. S7: Phantoms MRI of SiO₂-Gd-NPs *vs.* free Gd-HP-DO3A *vs.* water. Fig. S8: BET characterizations. Fig. S9: *In vivo* FLI. Fig. S10: *Ex vivo* FLI of organs of interest (after 14 days). Fig. S11: *In vivo* MRI examination at 9.4 T. Fig. S12: Photoacoustic imaging experiments: PA spectra recorded on phantom images of NIR-dye PEG-coated SiO₂-Gd-NPs at various concentrations and evolution of MSOT signal (770 nm). See DOI: 10.1039/d1nr04972k



branes for ultrafiltration (MWCO = 100 kDa) were purchased from Merck Millipore (USA) and Metrohm (Belgium). Membranes Spectre/Por® (MWCO = 12–14 kDa) for dialysis were acquired from VWR (Belgium).

Inorganic core preparation. Empty spherical SiO₂-NPs were prepared through a reverse microemulsion-mediated pathway using TEOS as a silica precursor and ammonia as a catalyst. The emulsion involved a mixture of cyclohexane (9 mL), hexane-1-ol (2 mL), Triton™ X-100 (2 mL) and deionized (DI) water (1 mL) under magnetic stirring at room temperature for 30 minutes. Subsequently, tetraethoxysilane (TEOS; 0.44 mmol; 100 µL) was dropped into the mixture and kept under stirring for a further 30 minutes. Ammonia (30–33%; 60 µL) was then added and the media was left at room temperature for 24 hours under gentle magnetic stirring.

Surface modification of SiO₂-NPs. The silica surface was reactivated by adding TEOS (0.22 mmol; 50 μ L) to the mixture followed by silane methoxypolyethylene glycol 2 kDa (36 μ mol; 75 mg) after 30 minutes to produce a homogeneous system. The mixture was stirred for 24 hours. Finally, PEG-coated SiO₂-NPs were isolated by precipitation into acetone/diethyl ether mixture (1:1, v/v), washed five times with acetone, and finally resuspended in DI water (5 mL). The resulting suspension was dialyzed (MWCO = 12–14 kDa) at 35 °C against DI water to remove physisorbed species. After the purification steps, the suspension was centrifuged (2700 g, 5 minutes) to remove any agglomerates and the supernatant was carefully separated and characterized. ¹H NMR (500 MHz, D₂O) δ (ppm): [3.7–3.5] (m); 3.4 (s, 3H); 1.6 (q, 2H, J = 7.7 Hz); 0.6 (t, 2H, J = 7.9 Hz).

Carboxylic functions were introduced onto PEG-coated SiO₂ nanoparticles by mean of a photochemical treatment in the presence of a carboxylated diazirine system. The UV-sensitive 4-(3-diazirin-3-yl)benzoic acid (3*H*-DiazBA) crosslinker was solubilized in acetonitrile and the same volume of nanoparticle suspension (1%_{wt/v}) was added to obtain a composition of acetonitrile/DI water (1 : 1, v/v) using 20 μmol of 3*H*-DiazBA per milliliter of PEGylated particles suspension. The homogeneous mixture was then irradiated with ultra-violet light (365 nm) at a distance of 3 cm from the light source. Irradiance experiments were performed as a function of time under ambient atmosphere and continuous magnetic stirring. Hereafter, the samples treated with 3*H*-DiazBA were then dialyzed against deionized water (MWCO = 12–14 kDa). The concentration of carboxylated groups onto fully PEG-coated SiO₂-NPs was determined spectroscopically by following the UV absorbance peak of the linker (233 nm). The nanoparticle density was obtained gravimetrically after lyophilizing of the suspension followed by a drying step at 80 °C during 24 hours. ¹H NMR (500 MHz, D₂O) δ (ppm): 7.8 (d, *J* = 8.1 Hz); 7.4 (d, *J* =

Materials

Hexan-1-ol (99%), Triton™ X-100, ammonium hydroxide (30–33%), hydrochloric acid (37%), sulfuric acid (95%), gadolinium atomic absorption standard, acetone (97%), sodium phosphate monobasic monohydrate ($\text{NaH}_2\text{PO}_4 \cdot \text{H}_2\text{O}$, 98%) and sodium phosphate dibasic (Na_2HPO_4 , 99%) were purchased from Sigma-Aldrich (Belgium). Diethyl ether (99%) was obtained from Chem-Lab (Belgium). Tetraethoxysilane (TEOS, 99.9%) was obtained from Fluka (Belgium). Cyclohexane (99.9%) and acetonitrile (99.8%) were provided from VWR (Belgium). 3-[Methoxy(polyethylenec oxide)propyl] (triethoxysilylpropyl)carbamate (PEG, 2000 g mol⁻¹) was purchased from Biochempeg Scientific (USA). 4-(3-Diazirin-3-yl)benzoic acid (3*H*-DiazBA, 97%) was obtained from TCI Chemicals (Belgium). *N*-(3-Dimethylaminopropyl)-*N'*-ethylcarbodiimide hydrochloride (EDC·HCl) was purchased from Roth. ProHance® (Gd-HP-DO3A) was purchased from Altana Pharma (Belgium). All the materials mentioned above were used directly, without any further treatment. Stirred cells and mem-

8.1 Hz); [3.7–3.5] (m); 3.4 (s, 3H); 1.6 (q, $J = 7.7$ Hz); 0.6 (t, $J = 7.9$ Hz); ^{19}F NMR (470 MHz, D_2O) δ (ppm): 72.

Synthesis of paramagnetic silica nanoparticles (PEG-coated SiO_2 -Gd-NPs)

Stable paramagnetic SiO_2 -NPs were obtained by replacing water by a solution of Gd-HP-DO3A (1 mL) in the above-described protocol. To achieve optimal efficiency, three samples were prepared using 25, 50 and 100 mM Gd-HP-DO3A solution in deionized water. Optimizations were performed using three replicates in each condition.

Preparation of multimodal (fluorescent and paramagnetic) particles by the insertion of NIR-dyes onto functionalized PEG-coated SiO_2 -Gd-NPs (NIR-dye PEG-coated SiO_2 -Gd-NPs)

Synthesis of NIR-dye. The fluorescent NIR-dye was synthesized according to the route adapted from Choi *et al.*,^{37,38} and described in a recent paper.³⁹ λ_{max} Vis/NIR (abs/em) in H_2O (nm): 764/785.


Dye coupling. Dark glassware was used to prevent photodegradation of the fluorophore during the surface coupling and purification steps. Amine-bearing NIR-dye were grafted onto carboxylated PEG-coated SiO_2 -Gd-NPs using carbodiimide chemistry with EDC as a coupling agent. Optimal coupling reactions were obtained using Sorensen buffer (pH 5.8; 25 °C) as described elsewhere.²⁴ The coupling started with the addition of the NIR-dye (4.5 μmol ; 5 mg) in buffered suspension of particles, followed by *N*-(3-dimethylaminopropyl)-*N'*-

ethylcarbodiimide hydrochloride (EDC; 250 μmol ; 24 mg). The reaction mixture was maintained under magnetic stirring for 4 h at room temperature. Subsequently, another addition of EDC (250 μmol ; 24 mg) was added to the media for a further 4 h. Ungrafted compounds were removed from the suspension by dialysis (MWCO = 12–14 kDa) followed by membrane filtration (MWCO = 30 kDa) until no emission signal could be detected. To ensure the efficiency of the process, a negative control working with a non-EDC activated conditions was performed. Finally, the nanoparticles were concentrated to 3 mL by stirred ultrafiltration cell device (Merck Millipore).

The entire synthetic process for the preparation of such particles is summarized in Scheme 1.

Instrumentation

Characterization techniques. Zeta potential and dynamic light scattering (DLS) measurements of nanoparticles suspensions were conducted using a Zetasizer Nano ZS particle size analyzer (He-Ne laser, 633 nm) (Malvern Instruments, Worcestershire, UK) on diluted suspensions (1 mg mL^{-1}). The mean hydrodynamic diameter size ($D_{\text{H}}^{\text{DLS}}$), the size distribution and the polydispersity index (PDI^{DLS}) of a particle suspension were measured in aqueous media (water and 0.9% NaCl) at 25 °C. Transmission electron microscopy (TEM) images were recorded to determine particle morphological details using a Fei Tecnai 10 microscope (Oregon, USA) working at an operating voltage of 80 kV. Each TEM specimen was prepared using silica suspension (20–25 mg mL^{-1}) that was dropped onto

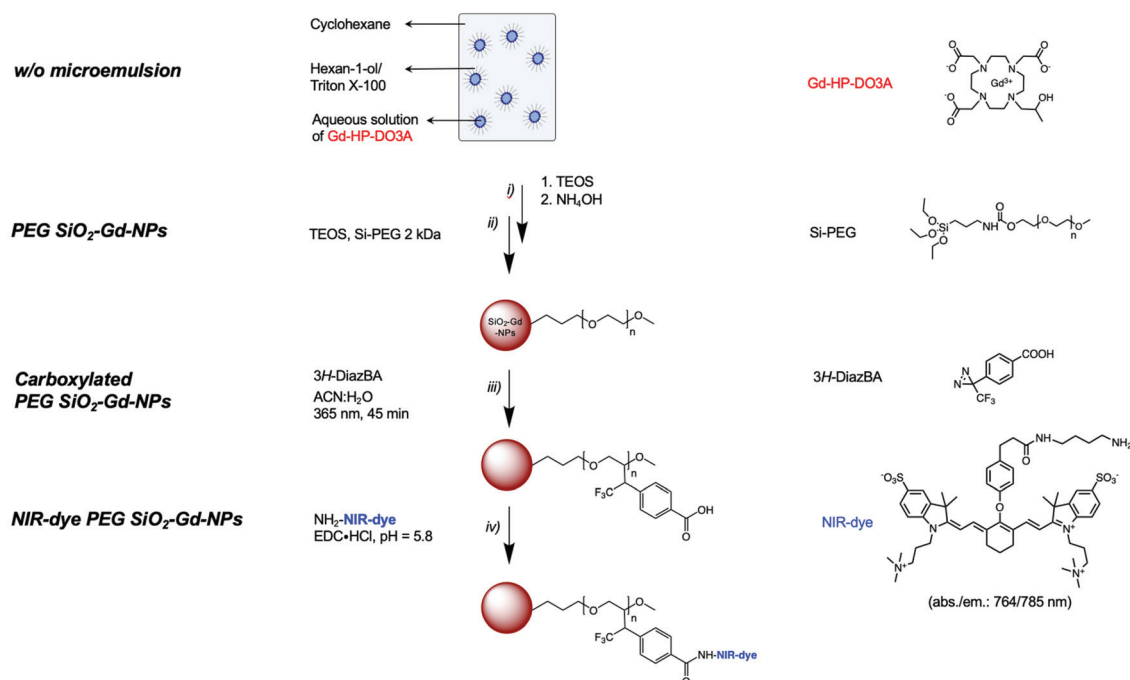

Scheme 1 Schematic synthetic route leading to the proposed multimodal nanoplatfrom (NIR-dye PEG-coated SiO_2 -Gd-NPs). Step (i): Formation of the w/o microemulsion with encapsulation process during SiO_2 -NPs formation; step (ii): hydrolysis and condensation of the silica precursor into aqueous nanoreactors and PEGylation of the nanospheres; step (iii): functionalization through UV-sensitive carboxylated diazirine linker insertion and step (iv): grafting of compounds of interest (fluorescent molecule).



and 60 μL of deuterated solvent. The spectra were recorded at 25 $^{\circ}\text{C}$ in $\text{H}_2\text{O}/\text{D}_2\text{O}$ (10%) using water ^1H NMR peak suppression sequence. Chemical shifts (δ) are presented in parts per million (ppm) referenced to D_2O (4.79 ppm, ^1H NMR) as the internal reference. Coupling constants (J in Hz) on ^1H NMR are given in hertz and the resonance multiplicity is described as s (singlet), d (doublet), t (triplet), q (quintuplet), m (multiplet).

NMR self-diffusion measurements as diffusion ordered spectroscopy (DOSY-NMR) experiments were conducted at 25 °C on a 600 MHz Bruker Avance spectrometer (Bruker, Germany) equipped with a field gradient probe using a 2D STE-LED (stimulated echo-longitudinal eddy current delay) sequence with a gradient pulse length (δ) of 4 ms, a diffusion time (Δ) of 500 ms and gradients ranging from 2% to 95%. The translational diffusion coefficients (D in $\text{cm}^2 \text{s}^{-1}$) were obtained using the following relation,⁴² (eqn (4))

Thermogravimetric analyses (TGA) were performed on a TA Q500 device (TA Instruments, New Castle, United States) in an ambient atmosphere. Suspensions were dried, and the as-obtained powders (10 mg) were disposed of in a Platine crucible. Samples were first heated at 120 °C for 10 minutes at a temperature elevation rate of 10 °C per minute with an air flow of 25 mL min⁻¹ to prevent solvent residues. Then, a temperature of 600 °C was reached (heating rate of 10 °C min⁻¹) and maintained for 5 minutes. The mass loss was monitored over the process. The number of PEG chains (n_{PEG}) anchored onto the silica surface per particle has been estimated through thermogravimetric analysis using the following equations as referred to in previously published references.^{40,41} Since the organic-to-inorganic ratio is measured from weight loss on the experimental TGA curve and the molecular weight of the coating molecule ($M_{\text{w}}^{\text{PEG}}$) is known as shown below (eqn. (1))

where it can be assumed that the molecular weight of the silica nanoparticles (M_w^{NPs}), represented as nonporous spheres, is approximated with this next relation (eqn (2))

where ρ is the mass density of silica oxide (2.4×10^{-21} g nm $^{-3}$), N_A is the Avogadro number and r_{NPs} is the particle radius estimated by TEM measurements.

Finally, the PEG chain density onto a single particle (D_{PEG} [chain per mm^2]) was estimated as (eqn (3))

Proton and fluorine NMR spectra were acquired using a 500 MHz Bruker Avance II instrument (Bruker, Germany) operating at 500.13 MHz (^1H) and 470.59 MHz (^{19}F). NMR samples were obtained by mixing 540 μl of concentrated NP suspension

where I and I_0 are the echo intensities in the presence and absence of pulse gradients, respectively; $q = \gamma g \delta$; γ is the gyromagnetic ratio of the nucleus under investigation and g is the gradient strength.

Spectroscopic measurements were recorded at room temperature. The crosslinker molecule was quantified by UV absorbance measurements (230 nm) after solubilizing various concentration of 3*H*-DiazBA for establishing a linear calibration curve (coefficient of determination, $R^2 > 0.99$). The absorbance of the NP samples treated with the linker in CH₃CN/H₂O (1 : 1, v/v) was compared to determine their concentration. Absorbance properties were characterized by a Lambda 35 UV-visible spectrometer (PerkinElmer, Wellesley, MA) with a scanning rate set at 480 nm min⁻¹. Silica contribution was subtracted from the absorbance background. Following the similar procedure described in the quantification of the linker, the content of grafted dyes was reached (764 nm). Emission spectra in the NIR range were recorded on a PerkinElmer LS 55 spectrofluorimeter equipped with a R928 photomultiplier (PerkinElmer, USA). The excitation and emission slits were fixed to 10 nm and the scanning speed was set to 100 nm min⁻¹.

Infrared (IR) spectra were recorded on a PerkinElmer FTIR Spectrum 100 (Manchester, UK).

The total gadolinium ion concentration of each sample was determined by inductively coupled plasma-atomic emission spectroscopy (ICP-AES) analysis under argon plasma on a Varian Liberty Series II instrument (Varian Inc., Palo Alto, USA). Briefly, the samples (500 μL) were digested in a mixture of H_2SO_4 (95%; 300 μL)/ HCl (37%; 300 μL) and exposed to microwave radiation using a Milestone MLS 1200 Mega microwave laboratory station (Analisis, Belgium). The volumes of the resulting acid-treated samples were adjusted to 5 mL using deionized water. Prior to quantification, standards were prepared from Gd^{3+} single element standard (1001 $\mu\text{g mL}^{-1}$) on diluted $\text{H}_2\text{SO}_4/\text{HCl}$ solution. Calibration curves ($R^2 > 0.99$) using

analyzed using M3Vision software (Biospace Lab) by drawing ROI around each well of the plate. The fluorescent signal was expressed as photons per second per square centimeter per steradian (ph per s per cm^2 per sr). Photoacoustic imaging, as multispectral optoacoustic tomography (MSOT), experiments were carried out on a InVision 256-TF instrument (iThera Medical GmbH, Munich, Germany). Samples were excited from 660 to 930 nm (5 nm steps) and data were analyzed using viewMSOT 4.0 software (iThera Medical). Optoacoustic signals were extracted as MSOT arbitrary unit (a.u.). All phantom images were recorded at several concentrations in order to compare the contrast generated by our agent.

Small animal imaging experiments. *In vivo* experiments were conducted at the Center for Microscopy and Molecular Imaging (CMMI, Gosselies, Belgium). Small animal procedures are carried out in accordance with experimental protocol “CMMI-2021-01” accepted by the ethics committee of CMMI (Laboratory Agreement, LA number 15005-89) following animal ethics rules of the European (86/609/CEE) and Belgian legislations.

MRI imaging. *In vivo* Magnetic resonance imaging was performed on 1 T and 9.4 T Bruker devices (ICON and Biospec, respectively) in healthy hairless SKH1 mice with a total of 6 ($n = 6$). Mice were kept anesthetized with isoflurane (2%) vaporized in oxygen (0.5 L min^{-1}) delivered through a system adapted for small animal body imaging, and mice temperature was maintained by a circulating water warming blanket (9.4 T) or bed (1 T). A catheter made of a 30G needle (B. Braun 100 Sterican) inserted in a tail vein and connected to a 29G syringe (Terumo U-100; containing the compound or flushing saline solution) *via* a polyethylene tube (Smiths (Portex); 0.28 mm internal diameter) allowing injection from outside the magnet, so that mice can remain in the same position between pre- and post-injection situation. During the whole experiment, the respiratory rate was monitored. The proposed multimodal agent was repeatedly intravenously injected in the tail vein of the animals in a volume of 100 μL ($n = 3$, 1 T experiments, thus 4.3 μmol of Gd^{3+} per kg weight) or 200 μL ($n = 3$, 9.4 T experiments, thus 8.6 μmol of Gd^{3+} per kg weight). At 1 T, T_1 -weighted images were collected pre-contrast (day 0) and from 3 minutes to 190 minutes post-injection, with 20 minutes between each acquisition. One additional acquisition was performed at day 1. Parameters at 1 T (RARE: TR = 300 ms, TE = 12 ms, NEX = 8, MTX = 128×216 , FOV = $3.30 \times 5.50 \text{ cm}$, slice thickness = 1.25 mm).

where T_i^{dia} are the proton relaxation times of the solvent as the diamagnetic contribution ($R_i^{\text{dia}} = 0.283 \text{ s}^{-1}$).

Due to stronger contrast effect at low field, main MRI experiments were carried out at 1 T, with an additional pre-injection and day 1 post-injection imaging session at 9.4 T. Signal enhancement at this higher field was nevertheless illustrated in some preliminary experiments after i.v. injection of a double dose (8.6 $\mu\text{mol Gd per kg}$) compared to 1 T MRI experiments, to compensate for the expected loss of contrast effect. This dose was fractionated in four sub-doses contained in roughly equal volumes (in fact corresponding to an injection of the total volume (200 μL) in four progressive steps, with an image acquisition after each step) to get basic visual infor-



Optical imaging. *In vivo* FLI experiments were performed using a Photon Imager Optima (Biospace Lab) loaded with 4-views module that allow simultaneous view of the fourth side of the mouse, and data analyze was performed using M3Vision software (Biospace Lab) (FLI, $\lambda = 712$ nm excitation, $\lambda = 797$ nm emission). 10 nmol of NIR-dye onto SiO₂-Gd-NPs (45 μ L, 230 μ M) was injected intravenously. Images were acquired before (pre-dye) and after injection from 5 min to up to 21 days. Mice (used for in FLI and supplementary mice) were sacrificed at different time-points post-injection (*i.e.*, 1 h, 1 day, 2 days, 2 weeks, 3 weeks).

Surface study: preparation of stable PEG-coated SiO₂-NPs

NMR (Fig. 3a) analysis were used to follow surface modification. First, the grafting of PEG onto the surface was assessed by the presence of the protons expected signals in NMR experiment. Thus, in addition to the presence of a signal at 3.6 ppm

Surface functionalization with carboxylic groups

The PEG-coated SiO₂-NPs were functionalized by a photochemical treatment using a carboxylated UV-sensitive crosslinker. The principle was to take advantage of a bi-reactive linker which owns an UV light activable function (diazirine) on one side and a reactive group (carboxylic function) on the other one. Under appropriate light, the linker leads to photogenerated carbene species which randomly insert on compound located at its close vicinity (*i.e.*, in C–H bonds from the polymer coating chain). In the present study, the grafting procedure implied the use of 4-[3-(trifluoromethyl)-3*H*-diazirin-3-yl]benzoic acid (3*H*-DiazBA) linker with a concentration of 2 μmol of 3*H*-DiazBA per milligram of PEGylated particles, and activated by irradiating the mixture at 365 nm at room temperature and directly in liquid media.^{55–57} The introduction of the linker on the particles was followed by UV spectroscopy thanks to appearance of a characteristic absorption peak at



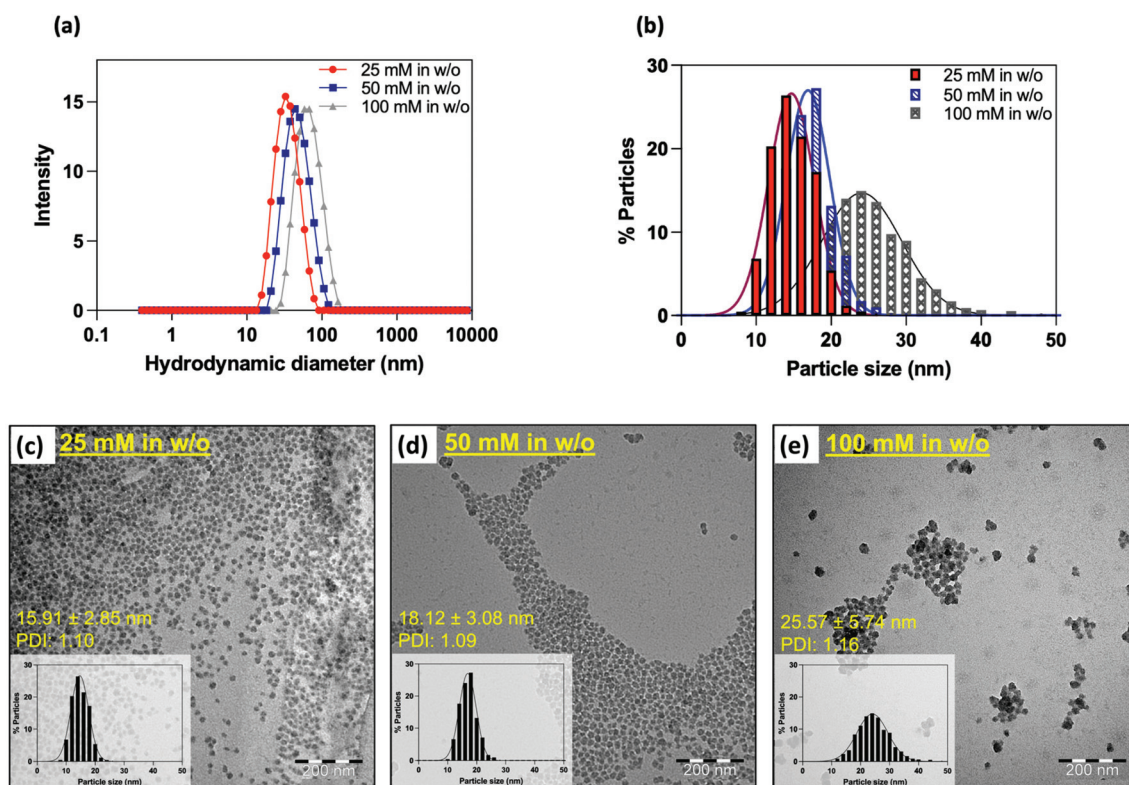


Fig. 4 Comparison of the NP size obtained as a result of the different encapsulation study. (a) Hydrodynamic size distributions (DLS, intensity-weighted) of NP^{16/18/25} nmGd particles in aqueous suspension. (b) Histogram of particle size distribution from TEM analysis of the synthesized NP^{16/18/25} nmGd. The mean particles diameter from statistical analysis of NP¹⁶ nmGd (25 mM in w/o) was 15.91 ± 2.85 nm, TEM polydispersity index (PDI^{TEM}): 1.10; D^{TEM} of NP¹⁸ nmGd (50 mM in w/o) = 18.12 ± 3.08 nm ($PDI^{TEM} = 1.09$); D^{TEM} of NP²⁵ nmGd (100 mM in w/o) = 25.57 ± 5.74 nm ($PDI^{TEM} = 1.16$). TEM images (scale bar: 200 nm) of the corresponding PEG-coated SiO₂-Gd-NPs obtained with (c) 25 mM in w/o, (d) 50 mM in w/o and (e) 100 mM in w/o (scale bar: 200 nm). Insets show the TEM size distributions determined by statistical analysis. Average D^{TEM} diameters were estimated over multiple TEM images recorded for each triplicate.

16 nm to 26 nm ($D^{TEM} = 15.9 \pm 2.8$ nm; $PDI^{TEM} = 1.1$; $D^{TEM} = 18.1 \pm 3.1$ nm; $PDI^{TEM} = 1.1$; $D^{TEM} = 25.6 \pm 5.7$ nm; $PDI^{TEM} = 1.2$). It may appear difficult to explain the reason of such size differences since microemulsion are dynamic systems. However, one must remember that the several experimental parameters such as the intra-micellar pH or the ionic strength have a strong influence on the hydrolysis and condensation of TEOS units, thus on the final particles properties.⁴⁸

The proton longitudinal relaxivities of the different samples were determined by means of the acquisition of their NMRD profiles measured at 37 °C on a per millimolar of Gd³⁺ basis (Fig. 5). First, it should be noted that all the prepared samples showed a significant increase in their r_1 values when compared to those of free Gd-HP-DO3A in all frequency ranges. Especially at approximately 20 MHz, these values are approximately 5 to 10 times higher than the value observed for the free complex and are 3 to 5-fold higher at 60 MHz. The shape of the overall curves alongside the appearance of a bump above 10 MHz suggest effective encapsulation within the matrix as well as efficient water exchange between the inner-particle water molecule and the outer-particle water.

A decrease in the r_1 values when increasing the size of the particle was observed as described elsewhere.³⁶ Since the Gd³⁺

concentration was determined by ICP-AES for each sample, an estimation of the amount of Gd-HP-DO3A chelates entrapped inside a single silica particle was approximated assuming that SiO₂-NP cores are monodisperse (ESI†). Herein, smaller NP¹⁶ nmGd systems carried out about ~80 complexes within their structure, whereas NP¹⁸ nmGd contained about more than ~130 and larger NP²⁵ nmGd about ~300. Thus, the r_1 increase may be attributed to the smaller particle size observed when incorporating a lower initial chelate concentration. Considering that the observed boost in relaxivity is the consequence of an increase in the rotational correlation time (inner-sphere effect), but also of an increase in the diffusion correlation time for water molecules (outer-sphere effect), which are confined and forced to interact for a longer period with the Gd complex adsorbed to the inner pore surface,⁵⁹ one may suggest that when decreasing the particle size, the chelates located on the outer particle shell contribute to the relaxation to a higher extent in comparison with the contribution of complexes embedded more deeply (Table 1). The coefficients of diffusion approximated from the fitting of NMRD profiles (Table 1; D^{NMRD}) confirm this trend by showing a significant increase (approx. 7 times) when comparing NP¹⁶ nmGd and NP²⁵ nmGd.



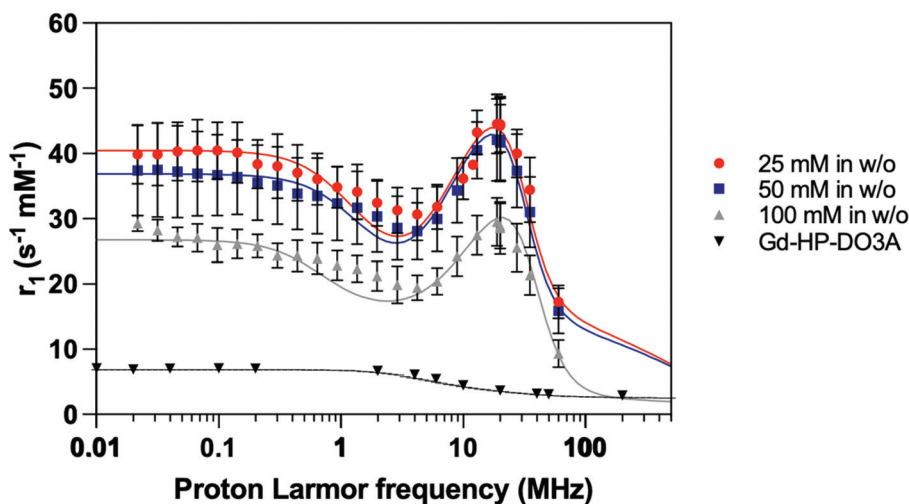


Fig. 5 NMRD profiles ($T = 37^\circ\text{C}$) obtained for the paramagnetic complexes entrapped on PEG-coated SiO_2 -Gd-NPs (16, 18 and 25 nm) as a result of [Gd-HP-DO3A] in w/o procedure (triangles, squares and squares on edge, respectively) and free Gd-HP-DO3A complex (circles) in aqueous solution. Longitudinal (r_1) relaxometric measurements plots are normalized per paramagnetic gadolinium ion concentration ($\text{s}^{-1}\text{mM}^{-1}$).

Table 1 Properties of the synthesized PEG-coated SiO_2 -Gd systems under different Gd-HP-DO3A concentration in w/o (average values of triplicate)

Samples (conditions during encapsulation)	Hydrodynamic diameter (intensity-weighted distribution)	Particle diameter		Relaxometric measurements ($T = 37\text{ }^{\circ}\text{C}$) ($\text{s}^{-1}\text{ mM}^{-1}$)				D^{NMRD} ($\text{cm}^2\text{ s}^{-1}$)
				$B_0 = 0.47\text{ T}$		$B_0 = 1.41\text{ T}$		
	$D_{\text{H}}^{\text{DLS}}$ (nm)	D^{TEM} (nm)	PDI	r_1^{para}	r_2^{para}	r_1^{para}	r_2^{para}	
25 mM	33.4 ± 1.2	15.9 ± 2.8	1.1	44.9 ± 2.4	61.1 ± 6.2	17.3 ± 2.5	127 ± 3	$2.5 \pm 0.1 \times 10^{-6}$
50 mM	39.1 ± 4.6	18.1 ± 3.1	1.1	42.2 ± 3.9	58.8 ± 11	15.9 ± 3.5	105 ± 3	$2.8 \pm 0.2 \times 10^{-6}$
100 mM	66.9 ± 4.7	25.6 ± 5.7	1.2	28.9 ± 3.4	43.8 ± 3.2	9.3 ± 2.1	95 ± 4	$1.9 \pm 0.04 \times 10^{-5}$
Gd-HP-DO3A	—	—	—	3.6	—	3.0	—	3.3×10^{-3}

The observations suggested efficient physico-chemical parameters of the synthesized PEG-coated SiO_2 -Gd-NPs systems using [Gd-HP-DO3A] = 25 mM in the encapsulation step. As a result, monodisperse and smaller NPs with a mean SiO_2 -Gd-NPs particles size of $15.9 \pm 2.8\text{ nm}$ (PDI^{TEM} : 1.1). From the analysis of the relaxometric properties, it appears that the proposed system shows similar or even better longitudinal relaxivities than systems decorated by Gd-chelates on their outer-shell.²⁵

The nitrogen adsorption and desorption isotherms are shown in Fig. SI 5.† Even if the SiO_2 -NPs produced by reverse microemulsion are supposed to be solid and not porous, the shape of the obtained isotherms suggests the formation of a mesoporous material.⁶⁰ The w/o encapsulation procedure leads thus to spherical nanomaterial characterized by small pores ($<2\text{ nm}$) which enable the diffusion of water molecules while restricting the diffusion of the chelates outside the matrix.

Preparation and characterizations of the proposed multimodal nanoplatform (NIR-dye PEG-coated SiO_2 -Gd-NPs)

With respect to MRI, optical imaging (OI) appears to be a complementary technique characterized by its high sensitivity.

Combining MRI and OI modalities within the same probe offers double tracking possibilities that are particularly useful for preclinical imaging studies. Near infrared absorbing/emitting chromophores (650–950 nm) are good candidates for *in vivo* imaging because of their minimal tissue absorbance and poor signal-to-noise ratio due to tissue autofluorescence. For this work, we were interested to work with an analog of indocyanine green (*i.e.*, the zwitterionic fluorophore indocyanine,^{37–39} Scheme 1), which is characterized by its remarkable physico-chemical properties (water solubility, high quantum yield, *etc.*) and great photostability.

To reach the desired platform, paramagnetic PEG-coated SiO_2 -Gd-NPs were prepared according to the conditions previously optimized. Briefly, Gd-HP-DO3A ($[\text{Gd}^{3+}] = 25\text{ mM}$ in w/o) was directly introduced during the microemulsion step, followed by the PEGylation. After purification, the PEG corona was modified by mean of a photochemical process using carboxylated diazirine. The targeted fluorescent properties were obtained by treating the resulting particles with the NIR-dye and EDC in Sorensen buffer. A similar sample without EDC was prepared in parallel in order to assess the efficiency of the grafting conditions and the purification process. After iso-



lation and purification of the resulting suspension, the bimodal SiO₂-NPs were characterized with respect to stability, morphology, relaxometry and spectroscopic properties. DLS measurements were performed before and after functionalization of the silica nanoparticles and assessed the stability of the suspensions in aqueous and physiological media (Fig. S6†). On the contrary to the control sample, the particles treated with EDC showed a strong absorption/emission signal after modification with the NIR-dye (Fig. S7a†). By absorption spectroscopy, we approximated a concentration of approximately 4 nmol mg⁻¹ of particles which correspond to the functionalization yield (relative to the quantified carboxylic functions) of 15% (~11 dyes per particle). Optical imaging analysis of the platform confirmed its detectability at concentrations as low as 5 nM in FLI after excitation at 687 nm (Fig. S7b and c†). The number of counted photons per unit of time per unit of area while taking into account the spherical field view of the camera (intensity; photons per s per cm² per sr) were plotted as a function of scanning wavelength in Fig. S7c.†

As expected according to previous physico-chemical characterizations, phantoms MRI experiments revealed a strong increase (*T*₁-W) or decrease (*T*₂-W) in the signal at high magnetic fields (1 T and at 9.4 Tesla) in-per Gd³⁺ in comparison to water (Fig. 6) and to free Gd-HP-DO3A (Fig. S8†).

Small animals MRI and optical imaging

In vivo evaluations were performed using preclinical MRI scanners (1 T and 9.4 T) and FLI devices. For biodistribution studies, this version of NIR-dye PEG-coated SiO₂-Gd-NPs was injected intravenously (i.v.) in the tail vein of healthy mice.

Short-term biodistribution studies were performed by FLI for up to three weeks after i.v. injection with NIR-dye PEG-SiO₂-Gd-NPs (0.9% NaCl) (Fig. S9†). FLI (phantoms,

in vivo and *ex vivo*) experiments on the SiO₂-NPs were carried out under excitation at 712 nm, and the fluorescence was collected at 797 nm. Measurement of signal intensity in the neck area were used as reference for blood circulating NIR-dye PEG-coated SiO₂-Gd-NPs. Following the i.v. administration, the whole body of mice become fluorescent, and signal was increased up to 100% at 5 min, the first measured timing (Fig. 7a). Then it started to decrease progressively to only reach the pre-i.v. level at the later timepoints, ±25% at 1 day, ±7% at 7 days ± 2% at 21 days. This indicates a long persistence life of our NPs into the blood stream. FLI images showed a fast and strong accumulation into the bladder from the first minutes that followed the injection to 30 min after (signal increased of 600%). Then mice were allowed to wake up, and the miction emptied the bladder to a far lower level. Kidneys were also highlighted after injection and the signal was maximal at the first imaging time (*i.e.*, 5 min) with an increase of signal intensity up to 150%. The residual signal significantly decreased of 80% after 24 h and reached the basal level (*i.e.*, the neck level). From this timing, kidneys could not be distinguished anymore on images. Signal decreased followed the same speed as the rest of the body (Fig. 7a). Bladder and kidneys observations suggest a fast clearance of a fraction of NP by the urinary tract. The liver was also highlighted from the first timing, but the signal decreased, as compared to kidneys and the neck, much slowly. At later timings (1 day and later), the liver is still well highlighted and can be detected to 7 days and more.

At different timing after injection (1 h, 1, 2, 14 and 21 days), mice were sacrificed after the study, and different organs of interest were collected and then directly visualized by *ex vivo* FLI. Signal was compared to organs coming from a non-injected mouse and expressed as ratio. One hour after injection, kidneys are very strongly fluorescent with an increase of

(a) SiO₂-Gd systems

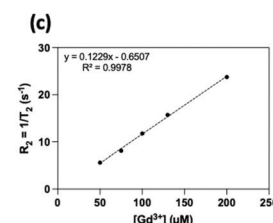
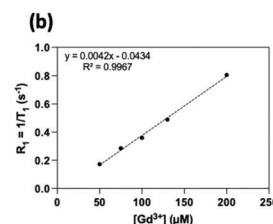
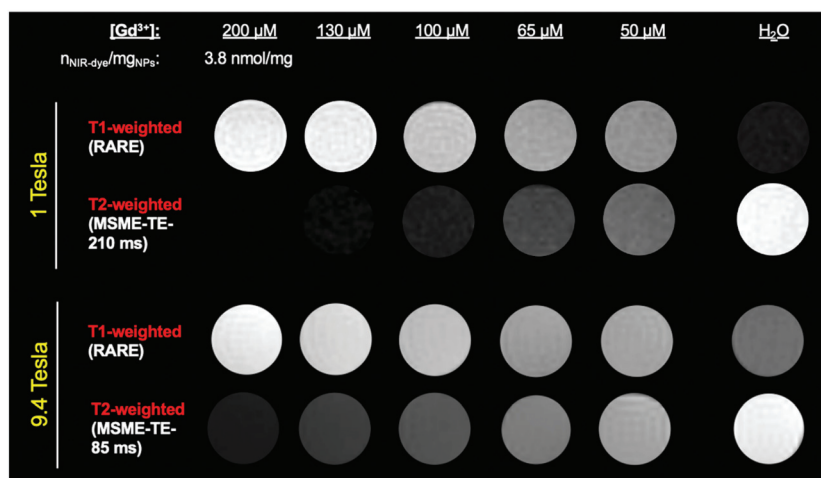


Fig. 6 (a) *T*₁- and *T*₂-weighted phantom MR images recorded at 1 T (42 MHz) and 9.4 T (400 MHz) of the synthesized MRI/OI multimodal silica probe from left to right, of a suspension of 200 μM of gadolinium (11 mg of particles per mL; 46 μM of SiO₂-NPs-anchored NIR-dye) and diluted samples. The images on the far right correspond to a phantom MR image of water (*T*₁-W, RARE sequence and *T*₂-W, MSME). Relaxation rates values showing the quantitative evolution of Gd³⁺ concentration-dependance using (b) *T*₁-W and (c) *T*₂-W (9.4 T).



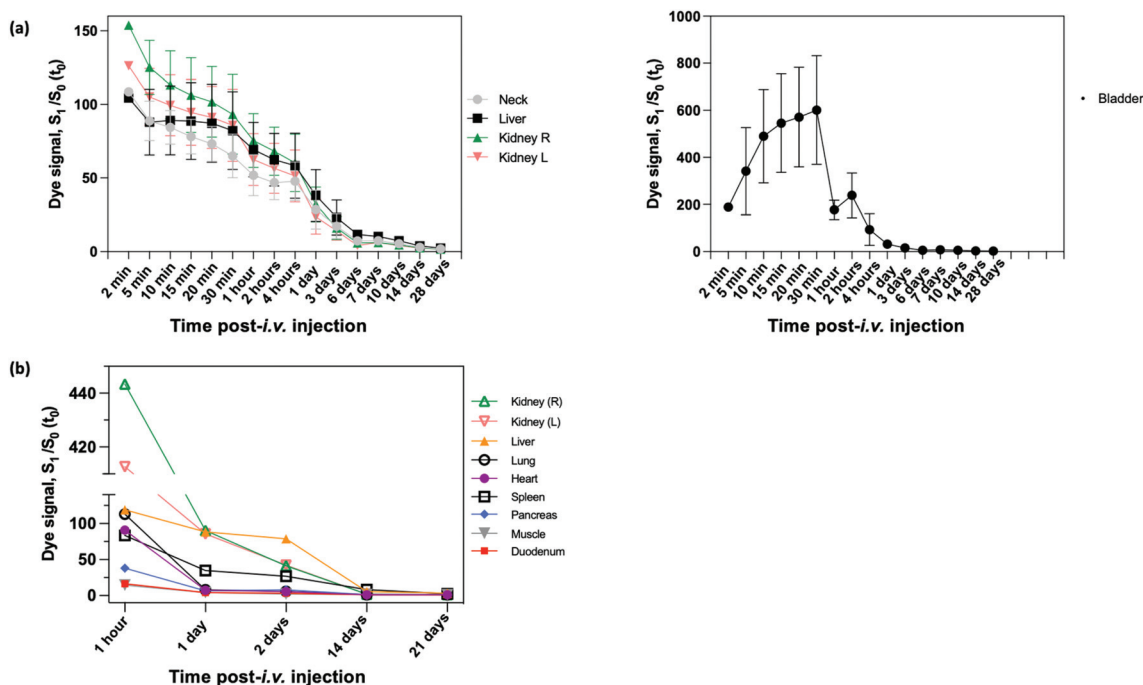


Fig. 7 (a) Evolution of the *in vivo* fluorescence intensity in neck, liver, kidneys over time from pre-i.v., to 28 days post-injection ($n = 3$). (b) *Ex vivo* FLI signal decrease for 1 hour to 21 days after the injection ($n = 3$).

fluorescence intensities (more than 400 higher), while spleen, lungs, heart, liver showed a strong and similar fluorescence intensities (± 100 -fold increase) (Fig. 7b). Pancreas showed a moderate fluorescent intensity (40-fold increase), and duodenum and muscle the weaker ones (± 15 -fold increase). At 1 day, fluorescence intensities of heart, lungs, pancreas, duodenum and muscle decreased to reach similar values comprised between 5 to 10-fold. Interestingly, fluorescence intensities of kidneys dropped strongly to ± 90 -fold, while the liver on decreased only a little to reach also 90-fold. Fluorescence intensity of spleen decreased also more slowly than most of organs and reach 35-fold. Two days after injection, fluorescence intensity of kidneys continued to fall down, while the liver and spleen were stable. At 2 weeks, most organs (heart, lungs, muscle, duodenum, pancreas and kidneys) reached the control level, while the fluorescence signal of liver is still 5 $\times$ higher, and interestingly the signal of spleen 8-fold time higher. Finally, spleen and liver are still weakly fluorescent (ratio of ± 3) 3 weeks after the injection. Taking together, these *ex vivo* results confirmed *in vivo* observation. They showed the intense passage of NPs through kidneys just after injection, and a liver and spleen accumulation a later timepoints. As compared to muscle as reference organ, there is no specific accumulation into duodenum, lungs, heart, pancreas. Consequently, it seems that a fraction of NPs is cleared by renal clearance path in the minutes/hour following injection, and then the persistence fraction of NP accumulated into liver and spleen. As there is no signal in pancreas and duodenum, the biliary pathway could be excluded as excretion route.

Weeks after the injection, animals were sacrificed after the study and different organs of interest were collected in accordance to previously described ethical protocol of the CMMI. These include muscle, lung, heart, duodenum, spleen, pancreas, gall bladder, liver, adrenal gland (right and left) and kidney (right and left) were visualized by FLI (Fig. S10†). In the spleen from day 14 to day 21 a decrease of 75% was observed.

Vascular enhancement in the 3 first post-injection hours was monitored with MRI on inferior vena cava in SKH mice and in main organs implied in nanoparticles elimination and possible storage/metabolization (kidney, liver). Despite a low Gd dose (4.3 μmol Gd per kg) regarding usually injected contrast agents (tens of μmol per kg), satisfying MR T_1 (positive) signal enhancement was measured in vena cava and represented as the evolution of signal intensity ratio between vena cava and an external reference, in percentage regarding the pre-injection value. Signal increase remained nonsignificantly fluctuating during the 3 h observation, thus stable around a 150% value. No more enhancement could be measured at day 1 after injection, suggesting that nanoparticles underwent restricted distribution (mainly vascular as could have been expected from their size) and apparently slow elimination from this compartment but significant enough to reduce their concentration below a detection threshold in MRI 24 h post-injection (Fig. 8a and b).

Signal measurements were also focused on kidney pelvis as a clue of their renal filtration and elimination. Represented as a value calculated the same way as from vena cava measurements, kidney pelvis enhancement was evident and remained around 90% during the 3 hours of observation, suggesting



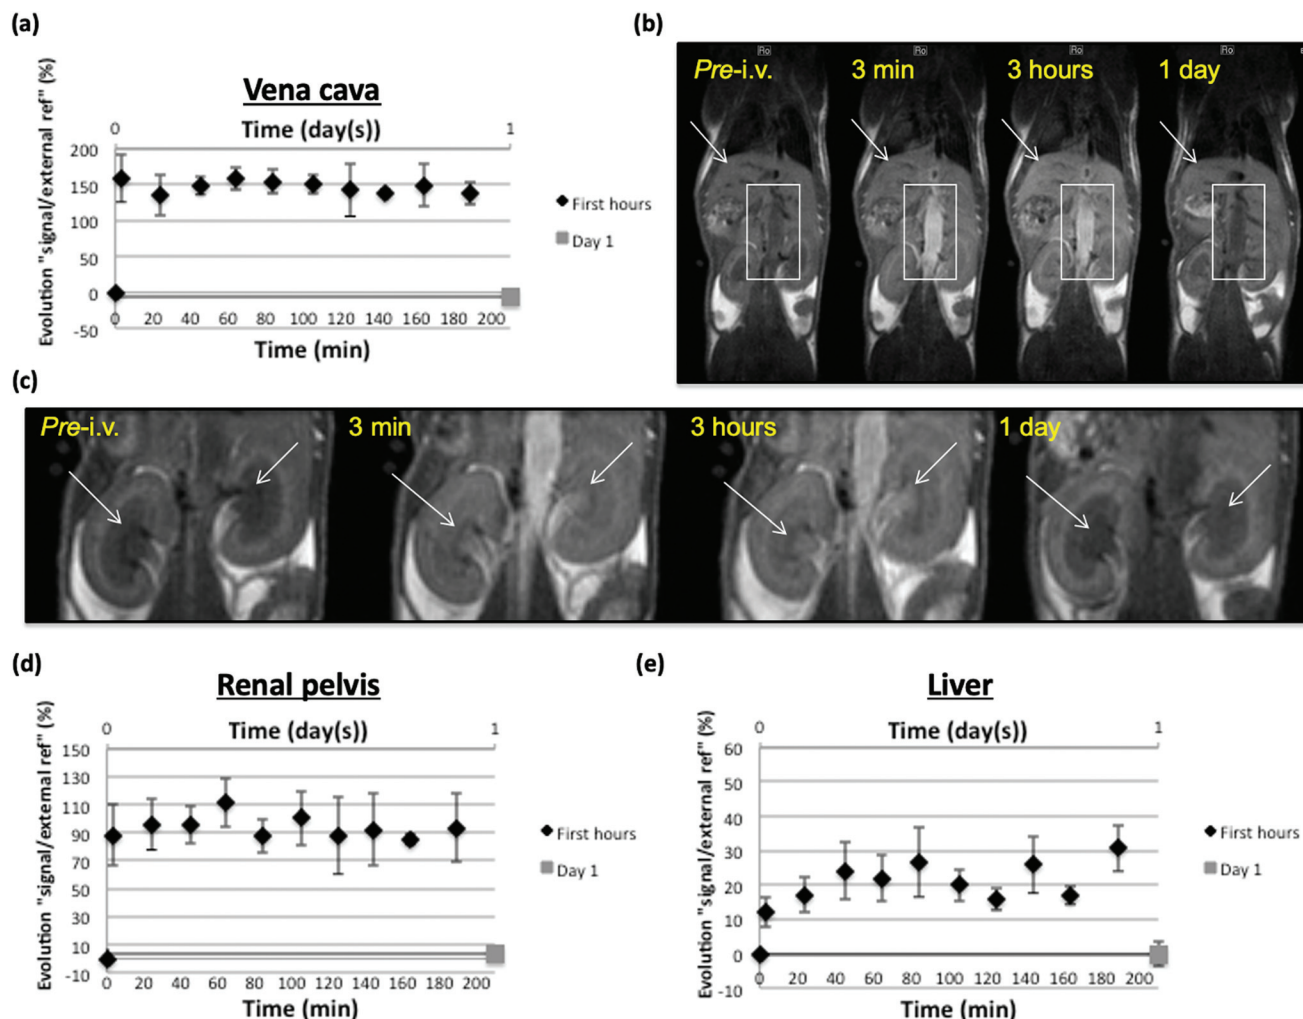


Fig. 8 Analysis of positive signal enhancement at 1 T and representative T_1 -weighted MR images before and during 3 first hours (black sign) + 1 day after (gray sign) i.v. injection of NIR-dye PEG-SiO₂-Gd-NPs ($4.3 \mu\text{mol kg}^{-1}$; signal enhancement data are normalized as a calculated ratio between respective signals in organs or vessel specific ROIs and in an external Gd-containing reference and represented as a percentage of the pre-injection value). (a) and (b) concern vena cava (surrounded by a white square); (c) and (d) concern renal pelvis (white arrow points at the renal pelvis); (e) and (f) concern the liver (white arrow points at the liver on (b)). Mean values $\pm$ std deviation of the mean are represented on graphs ($n = 3$).

ongoing renal elimination, allowed by nanoparticle properties (size, charge, shape) compatible with renal filtration of at least a part of the injected dose.⁶⁰ Again, the calculated value did not reflect any MRI detectable pelvis enhancement at day 1 post-injection, suggesting that most of kidney elimination of nanoparticles took place in this period of time, possibly due to their restricted distribution allowing them to mostly remain directly clearable from the blood vessels (Fig. 8c and d). As an important organ for distribution and clearance of nanoparticles, signal measurements were also focused on the liver. Liver is indeed a well perfused organ that has permeable vascularization (sinusoids), which is important for distribution aspects, and has cell populations (Kupffer cells, hepatocytes) that will allow uptake and possible storage/metabolization of the nanoparticles.⁶¹ At least, the calculated value reflecting signal enhancement in liver showed an increase that fluctuates (maybe due to respiratory motion in this part of the body, that

influences the measured signal) roughly between 15 and 30% regarding pre-injection value. This enhancement appeared to be simultaneous to the vascular enhancement observed during 3 hours, suggesting that it was related to the nanoparticle content of blood and thus to the local distribution of this compound due to liver perfusion and vessel permeability. At day one, calculated enhancement did not suggest any MRI detectable liver retention of nanoparticles (Fig. 8e). It would have been expected that a portion of the nanoparticle dose remain in liver sinusoids, possibly taken up by Kupffer cells and/or hepatocytes, but the amount of compound may be too low to induce sufficient contrast in the T_1 -weighted imaging conditions used (indeed, the PEG coating is expected to reduce such capture phenomena).⁶²

It may also be that the MRI contrast effect of nanoparticles is decreased when stored and/or metabolized in the liver but it has to be further investigated. Negative (T_2) contrast could



From observations performed at 1 T and 9.4 T with NPs after i.v. injection and from their relaxometric properties at those fields, it may be suggested that *in vivo* experiments seeking T_1 (positive) contrast should be performed at 1 T with an adequate dose; that can indeed be relatively low (4.3 μmol Gd per kg) compared to usual Gd chelates (around 100 μmol Gd per kg). Their T_2 effect is stronger at 9.4 T and negative contrast should thus more evidently take place (maybe partially masking positive effect) than at 1 T. However, tissues also have shorter T_2 at higher field strength, which narrows possibility of T_2 contrast, especially in the liver where NP accumulation can usually be expected. NP-induced T_2 contrast was indeed only depicted in long T_2 area; the renal pelvis. Conditions for T_2 contrast appear to be a compromise between injected dose, amount of accumulated NPs and basal relaxometric properties of the tissue where they (momentarily) accumulate. It has to be noticed that performances (signal/noise ratio, resolution) are lower on the ICON (1 T) regarding the Biospec (9.4 T), and that may also influence the selection of one or the other scanner for *in vivo* experiments with those NPs depending on requested image precision.

In this study, the noncovalent incorporation of Gd-HP-DO3A chelates into PEG-coated silica nanoparticles through a w/o microemulsion procedure was investigated. By doing so, stable suspensions exhibiting significantly improved relaxivity values

The authors thank the Center for Microscopy and Molecular Imaging (CMMI, supported by the European Regional Development Fund and the Walloon Region). The authors would like to acknowledge the unit of Therapeutic Chemistry and Pharmacognosy (Pr. P. Duez; UMONS) for the access to ICP-AES instrument and Mr C. Palmieri and Ms. G. Ayata for their investment and participation in the ICP characterizations. The authors are also grateful to the laboratory of Polymeric and Composite Materials (Pr. J.-M. Raquez; UMONS) and Dr S. Benali for the use of TGA equipment. Ms. C. Pierart is acknowledged for the record of NMRD profiles.

- 19 O. M. Koo, I. Rubinstein and H. Onyuksel, *Nanomedicine*, 2005, **1**, 193–212.
- 20 D. Pan, G. M. Lanza, S. A. Wickline and S. D. Caruthers, *Eur. J. Radiol.*, 2009, **70**, 274–285.
- 21 D. Zhu, F. Liu, L. Ma, D. Liu and Z. Wang, *IJMS*, 2013, **14**, 10591–10607.
- 22 M. Kaasalainen, V. Aseyev, E. von Haartman, D. Ş. Karaman, E. Mäkilä, H. Tenhu, J. Rosenholm and J. Salonen, *Nanoscale Res. Lett.*, 2017, **12**, 74–84.
- 23 T. Yu, A. Malugin and H. Ghandehari, *ACS Nano*, 2011, **5**, 5717–5728.
- 24 V. Balakrishnan, H. A. Ab Wab, K. Abdul Razak and S. Shamsuddin, *J. Nanomater.*, 2013, **2013**, 1–8.
- 25 E. Lipani, S. Laurent, M. Surin, L. Vander Elst, P. Leclère and R. N. Muller, *Langmuir*, 2013, **29**, 3419–3427.
- 26 F. Carniato, M. Muñoz-Úbeda, L. Tei and M. Botta, *Dalton Trans.*, 2015, **44**, 17927–17931.
- 27 C. Guo, J. Hu, A. Bains, D. Pan, K. Luo, N. Li and Z. Gu, *J. Mater. Chem. B*, 2016, **4**, 2322–2331.
- 28 F. Carniato, L. Tei, J. Martinelli and M. Botta, *Eur. J. Inorg. Chem.*, 2018, **8**.
- 29 F. Carniato, L. Tei and M. Botta, *Eur. J. Inorg. Chem.*, 2018, **2018**, 4936–4954.
- 30 P. Mathieu, M. Chalet, M. M. Clain, L. Teulon, E. Benoist, N. Leygue, C. Picard, S. Boutry, S. Laurent, D. Stanicki, C. Hénoumont, F. Novio, J. Lorenzo, D. Montpeyó, D. Ciuculescu-Pradines and C. Amiens, *New J. Chem.*, 2020, **44**, 18031–18047.
- 31 S. L. C. Pinho, H. Faneca, C. F. G. C. Geraldés, J. Rocha, L. D. Carlos and M.-H. Delville, *Eur. J. Inorg. Chem.*, 2012, **2012**, 2828–2837.
- 32 R. P. Bagwe, C. Yang, L. R. Hilliard and W. Tan, *Langmuir*, 2004, **20**, 8336–8342.
- 33 W. J. Rieter, J. S. Kim, K. M. L. Taylor, H. An, W. Lin, T. Tarrant and W. Lin, *Angew. Chem., Int. Ed.*, 2007, **46**, 3680–3682.
- 34 S. Santra, R. P. Bagwe, D. Dutta, J. T. Stanley, G. A. Walter, W. Tan, B. M. Moudgil and R. A. Mericle, *Adv. Mater.*, 2005, **17**, 2165–2169.
- 35 X. He, X. Wu, K. Wang, B. Shi and L. Hai, *Biomaterials*, 2009, **30**, 5601–5609.
- 36 N. Wartenberg, P. Fries, O. Raccurt, A. Guillermo, D. Imbert and M. Mazzanti, *Chem. – Eur. J.*, 2013, **19**, 6980–6983.
- 37 H. Hyun, M. W. Bordo, K. Nasr, D. Feith, J. H. Lee, S. H. Kim, Y. Ashitate, L. A. Moffitt, M. Rosenberg, M. Henary, H. S. Choi and J. V. Frangioni, *Contrast Media Mol. Imaging*, 2012, **7**, 516–524.
- 38 H. S. Choi, S. L. Gibbs, J. H. Lee, S. H. Kim, Y. Ashitate, F. Liu, H. Hyun, G. Park, Y. Xie, S. Bae, M. Henary and J. V. Frangioni, *Nat. Biotechnol.*, 2013, **31**, 148–153.
- 39 D. Stanicki, L. Larbanoix, S. Boutry, T. Vangijzegem, I. Ternad, S. Garifo, R. N. Muller and S. Laurent, *J. Mater. Chem. B*, 2021, **9**, 5055–5068.
- 40 A. Hannecart, D. Stanicki, L. Vander Elst, R. N. Muller, S. Lecommandoux, J. Thévenot, C. Bonduelle, A. Trotier,

- 1 S. Laurent, C. Henoumont, D. Stanicki, S. Boutry, E. Lipani, S. Belaid, R. N. Muller and L. Vander Elst, *MRI Contrast Agents: From Molecules to Particles*, 2017.
- 2 D. W. McRobbie, *MRI from picture to proton*, Cambridge University Press, Cambridge, UK, New York, 2006.
- 3 P. Caravan, J. J. Ellison, T. J. McMurry and R. B. Lauffer, *Chem. Rev.*, 1999, **99**, 2293–2352.
- 4 V. M. Runge, *Invest. Radiol.*, 2016, **51**, 273–279.
- 5 V. C. Pierre, M. J. Allen and P. Caravan, *J. Biol. Inorg. Chem.*, 2014, **19**, 127–131.
- 6 E. Blumfield, D. W. Swenson, R. S. Iyer and A. L. Stanesco, *Pediatr. Radiol.*, 2019, **49**, 448–457.
- 7 P. Caravan, C. T. Farrar, L. Frullano and R. Uppal, *Contrast Media Mol. Imaging*, 2009, **4**, 89–100.
- 8 *Cancer therapeutics and imaging: molecular and cellular engineering and nanobiomedicine*, ed. K. Rege and S. Goklany, World Scientific, New Jersey, 2017.
- 9 P. Caravan, *Acc. Chem. Res.*, 2009, **42**, 851–862.
- 10 E. Boros and P. Caravan, *J. Med. Chem.*, 2013, **56**, 1782–1786.
- 11 L. Tang and J. Cheng, *Nano Today*, 2013, **8**, 290–312.
- 12 S. Gündüz, T. Savić, D. Toljić and G. Angelovski, *JoVE*, 2016, 54776–54786.
- 13 J. Pellico, C. M. Ellis and J. J. Davis, *Contrast Media Mol. Imaging*, 2019, **2019**, 1–13.
- 14 W. Zhang, L. Liu, H. Chen, K. Hu, I. Delahunty, S. Gao and J. Xie, *Theranostics*, 2018, **8**, 2521–2548.
- 15 N. Kamaly and A. D. Miller, *Int. J. Mol. Sci.*, 2010, **11**, 1759–1776.
- 16 S. Aime, C. Cabella, S. Colombatto, S. Geninatti Crich, E. Gianolio and F. Maggioni, *J. Magn. Reson.*, 2002, **16**, 394–406.
- 17 J. C. Cutrin, S. G. Crich, D. Burghelea, W. Dastrù and S. Aime, *Mol. Pharm.*, 2013, **10**, 2079–2085.
- 18 Z. Cheng, A. Al Zaki, I. W. Jones, H. K. Hall, C. A. Aspinwall and A. Tsourkas, *Chem. Commun.*, 2014, **50**, 2502–2505.

- P. Massot, S. Miraux, O. Sandre and S. Laurent, *Nanoscale*, 2015, **7**, 3754–3767.
- 41 T. Vangijzegem, D. Stanicki, S. Boutry, Q. Paternoster, L. Vander Elst, R. N. Muller and S. Laurent, *Nanotechnology*, 2018, **29**, 265103–265117.
 - 42 R. Colsenet, O. Söderman and F. Mariette, *Macromolecules*, 2006, **39**, 1053–1059.
 - 43 C. J. Brinker, *J. Non-Cryst. Solids*, 1988, **100**, 31–50.
 - 44 E. A. Hauser, *Clays Clay Miner.*, 1955, **4**, 45–53.
 - 45 S. Chatterji, *Cem. Concr. Compos.*, 2005, **27**, 788–795.
 - 46 C.-L. Chang and H. S. Fogler, *AIChE J.*, 1996, **42**, 3153–3163.
 - 47 M. A. López-Quintela, C. Tojo, M. C. Blanco, L. García Rio and J. R. Leis, *Curr. Opin. Colloid Interface Sci.*, 2004, **9**, 264–278.
 - 48 K. S. Finnie, J. R. Bartlett, C. J. A. Barbé and L. Kong, *Langmuir*, 2007, **23**, 3017–3024.
 - 49 C. Aubery, C. Solans, S. Prevost, M. Gradzielski and M. Sanchez-Dominguez, *Langmuir*, 2013, **29**, 1779–1789.
 - 50 R. Michel, S. Pasche, M. Textor and D. G. Castner, *Langmuir*, 2005, **21**, 12327–12332.
 - 51 P. Charles, V. Stubbs, C. Soto, B. Martin, B. White and C. Taitt, *Sensors*, 2009, **9**, 645–655.
 - 52 S. M. S. Björkegren, L. Nordstierna, A. Törnecrona, M. E. Persson and A. E. C. Palmqvist, *J. Colloid Interface Sci.*, 2015, **452**, 215–223.
 - 53 C. Bernhard, S. J. Roeters, J. Franz, T. Weidner, M. Bonn and G. Gonella, *Phys. Chem. Chem. Phys.*, 2017, **19**, 28182–28188.
 - 54 V. Cauda, A. Schlossbauer and T. Bein, *Microporous Mesoporous Mater.*, 2010, **132**, 60–71.
 - 55 V. Pourcelle, C. S. Le Duff, H. Freichels, C. Jérôme and J. Marchand-Brynaert, *J. Fluorine Chem.*, 2012, **140**, 62–69.
 - 56 V. Pourcelle, S. Laurent, A. Welle, N. Vriamont, D. Stanicki, L. Vander Elst, R. N. Muller and J. Marchand-Brynaert, *Bioconjugate Chem.*, 2015, **26**, 822–829.
 - 57 L. Dubinsky, B. P. Krom and M. M. Meijler, *Bioorg. Med. Chem.*, 2012, **20**, 554–570.
 - 58 S. Liang, C. L. John, S. Xu, J. Chen, Y. Jin, Q. Yuan, W. Tan and J. X. Zhao, in *Advanced Fluorescence Reporters in Chemistry and Biology II*, ed. A. P. Demchenko, Springer Berlin Heidelberg, Berlin, Heidelberg, 2010, vol. 9, pp. 229–251.
 - 59 R. Sethi, J. S. Ananta, C. Karmonik, M. Zhong, S. H. Fung, X. Liu, K. Li, M. Ferrari, L. J. Wilson and P. Decuzzi, *Contrast Media Mol. Imaging*, 2012, **7**, 501–508.
 - 60 S. Swar, V. Mátková and I. Stibor, *Materials*, 2019, **12**, 3202.
 - 61 W. Poon, Y. N. Zhang, B. Ouyang, B. R. Kingston, J. L. Y. Wu, S. Wilhelm and W. C. W. Chan, *ACS Nano*, 2019, **13**, 5785–5798.
 - 62 H. Arami, A. Khandhar, D. Liggitt and K. M. Krishnan, *Chem. Soc. Rev.*, 2015, **44**, 8576–8607.

