


rsc.li/materials-advances

Diogo Dias, ^{ab} Leonor Resina, ^{abc} Frederico Castelo Ferreira,^{ab}
Paola Sanjuan-Alberte ^{*ab} and Teresa Esteves^{*ab}

Cancer remains one of the leading causes of death, with traditional therapy approaches facing limitations such as nonspecific systemic toxicity and acquired resistance. As alternative and adjuvant treatment modalities, poly(3,4-ethylenedioxythiophene) (PEDOT) nanoparticles (NPs) leverage unique biocompatible, electrical, and thermal properties for combined imaging, controlled drug release and localised photothermal ablation. This review provides a comprehensive analysis of formulation of tailored PEDOT NPs as smart theragnostic agents toward precise, personalised nanomedicine. We outline common chemical and electrochemical synthesis techniques to control NP size, morphology, stability, and surface chemistry. Extensive structural and electrochemical characterisation relates polymerisation conditions to resultant properties. In particular, PEDOT NPs exhibit efficient near-infrared (NIR) absorption and photothermal conversion, enabling selective photothermal tumour ablation. Their intrinsic conductivity also enables electrical stimulation triggers to modulate the release of therapeutic payloads. While initial works confirm the potential of PEDOT NPs for spatiotemporal cancer treatment, clinical translation remains limited. Further efforts must focus on developing predictive preclinical models, scalable manufacturing methods and clinical partnerships to facilitate translation of these smart nanosystems from the laboratory to clinical use.

^cDepartament d'Enginyeria Química and Barcelona Research Center for Multiscale Science and Engineering, EEBE, Universitat Politècnica de Catalunya, C/Eduard Maristany 10-14, 08019, Barcelona, Spain



ials for healthcare applications, with a particular interest in anticancer therapies.



1. Introduction

Cancer is a multifaceted disease that remains one of the leading causes of death globally, with an estimated 10 million cancer deaths in 2020 according to the latest report by the World Health Organisation.¹ Despite significant advancements in cancer research and treatment options over the past decades, current therapeutic approaches such as chemotherapy, radiotherapy and surgery still face major challenges. These are related to non-specific systemic toxicity, acquired drug resistance, limited therapeutic efficacy, tumour microenvironment complexity, and patient-to-patient clinical variations. Furthermore, cancer recurrence and metastasis also contribute to the difficulty of developing effective treatment options.^{2–4} The need to address these has led to the development of novel, complementary

anticancer therapy strategies based on innovative approaches such as nanotechnology.

The field of nanomedicine, which involves the application of nanotechnology for diagnosis, monitoring, prevention, and treatment of diseases is becoming more promising.^{5–9} Nanoparticles (NPs), which are particles in the size range of 1–100 nm, have unique properties including a higher surface area-to-volume ratio, a quantum nature in the 1–10 nm range and capacity for encapsulating or adsorbing and transporting different substances, which make them promising theragnostic tools for tumour diagnosis and treatment.^{10–12} Due to their small size, NPs can selectively accumulate in tumours *via* the enhanced permeability and retention (EPR) effect, resulting in passive targeted delivery to cancer tissues.¹³ This is an effect that causes nanosized materials to preferentially accumulate in tumours due to their leaky vasculature and lack of lymphatic drainage.¹⁴ On the other hand, by introducing specific ligands that are recognised by commonly expressed cell-surface receptors on tumour cells, NPs can actively target tumours. Additionally, NPs can be designed with additional functionalities, including sustained and triggered drug release, imaging contrast, and photothermal ablation. Various NPs made from organic and inorganic materials have been developed for targeted delivery of chemotherapeutic drugs, immunotherapy agents, siRNA, microRNA, and other anti-cancer therapeutics.^{15,16}

NPs based on conductive polymers (CP) are an emerging class of organic nanomaterials, including polypyrrole (PPy), polydopamine (PDA), polyaniline (PANI), and poly(3,4-ethylenedioxythiophene) (PEDOT), which are among the highest attractive sensing materials due to their all-organic nature with intrinsic electrical conductivity, high signal transduction, optical transparency, mechanical flexibility, and chemical stability. These features primarily result from the fact that CPs contain a π -conjugated backbone, which is made up of alternating single (σ) and double (π) bonds along the polymer chain, enabling delocalised electron transfer.^{17,18} However, most CPs frequently



Frederico Castelo Ferreira

Frederico C. Ferreira completed his PhD in 2004 from Imperial College London (IC, UK), followed by a collaborative industrial post-doc between IC and Glaxo-SmithKline (2004–2006). He also holds a Master in Business and Administration (MBA) from New University of Lisbon (2008). Frederico is currently an Assistant Professor at the Instituto Superior Técnico and a member of the Institute of Bioengineering and Biosciences with diverse research interests including the development of externally responsive biomaterials, sustainable separations and biorefineries, and the production of sustainable and vegan scaffolds for cellular agriculture applications.

Frederico C. Ferreira completed his PhD in 2004 from Imperial College London (IC, UK), followed by a collaborative industrial post-doc between IC and Glaxo-SmithKline (2004–2006). He also holds a Master in Business and Administration (MBA) from New University of Lisbon (2008). Frederico is currently an Assistant Professor at the Instituto Superior Técnico and a member of the Institute of Bioengineering and Biosciences with diverse research



Paola Sanjuan-Alberte

electrochemical systems and their application in bioelectronic medicine.

Paola Sanjuan-Alberte is currently a “la Caixa” Junior Leader Fellow at the Institute for Bioengineering and Bioscience of Lisbon, Portugal, exploring nanobioelectronic systems for cancer therapy. She is a pharmacist by training who received an M.Pharm. degree in 2015 from the Universidad Santiago de Compostela, Spain. She was also awarded a PhD in 2019 from the University of Nottingham (UK) for her thesis on additive manufacturing of



Teresa Esteves

electrochemical systems and their application in bioelectronic medicine.

Teresa Esteves is currently a Researcher at the Institute for Bioengineering and Bioscience in Lisbon, Portugal. She has a PhD in Inorganic Chemistry from the University of Lisbon. Her research activities at the Bioengineering Department of Instituto Superior Técnico are focused on new material development for process design tackling challenging separations. She has expertise in chemical synthesis, nanomaterials formulation and charac-



need to be doped as the polymers lack charge carriers. The process of doping promotes the creation of radical cations/anions (polarons or bipolarons) in the backbone of the polymer, while counter-ions from the solution enter to balance the charge. The more extensive the doping process, the more electrically conductive CPs become.^{19,20}

PEDOT, a polythiophene (PTh) derivative, was first developed in the late 1980s by scientists at the laboratories of Bayer AG, and is usually doped with polystyrene sulfonate (PSS) to improve its solubility in water, as the negative charge in the sulfonate group stabilises the delocalised positive charge in PEDOT. PEDOT:PSS is the most water-soluble CP, which is crucial since materials that dissolve easily in water present easier processability.²¹ When synthesised as NPs, PEDOT is typically doped with chloride ions or dodecyl benzenesulfonate, the latter acting as doping agent and surfactant simultaneously.^{22–27}

PEDOT presents important advantages in comparison with other CPs like PPy and PANI, because of its biocompatibility, higher stability in biological environments, adjustable and higher electrical conductivity, electrochemical activity, thermoelectric behaviour, and high specific capacitance.^{23,28–30} For instance, unlike the most studied nontoxic CP, PPy, which is highly crosslinked, PEDOT's unique α,α linkages contribute to its superior electrochemical and electrical responses.²⁵ All the unique properties stated above not only make PEDOT NPs more attractive than similar NPs formed by other CPs, but have drawn attention from various fields where PEDOT NPs present many of their potential applications: flexible electronics,^{31,32} sensors,^{33–36} energy storage devices,^{37–39} and tissue engineering (spinal cord,⁴⁰ neural,^{41–43} muscle⁴⁴).

Additionally, studies have shown that PEDOT NPs exhibit strong near-infrared (NIR) absorption, efficient photothermal conversion that is higher than commercially available gold-based photothermal ablation agents, and tumour targeting *via* the EPR effect.^{45–47} These properties make PEDOT NPs an attractive candidate as photothermal agents for minimally invasive ablation of cancer cells. Furthermore, the versatile surface chemistry of PEDOT allows functionalisation with various functional groups, targeting ligands, imaging agents, and therapeutic drugs, allowing for targeted drug delivery and multimodal imaging.²⁸ These properties position PEDOT NPs at the forefront of personalised cancer nanomedicine, offering the potential for integrated therapy and diagnosis – a concept known as theragnostics.

Recent progress in the synthesis and application of PEDOT NPs has confirmed their efficacy in drug-delivery and photothermal therapy (PTT) for various types of cancer (Fig. 1). Therefore, a comprehensive review of PEDOT NP research focused on cancer therapy is justified.

Integrated nanosystems based on PEDOT NPs aim to leverage their unique properties by combining them with other functional elements to create a versatile platform capable of combining therapeutic treatments, targeted drug delivery and diagnostic imaging. This review will explore some examples, such as stimuli responsive nanocomposites that integrate PEDOT NPs into hydrogels or multifunctional nano- and

microfibrils; core-shell NPs with a magnetic core coated with a PEDOT shell; and theragnostic nanomicelles comprising a PEDOT NP core surrounded by an amphiphilic polymer shell (Fig. 1). Thus, a comprehensive understanding of the synthesis, characterisation, and properties of PEDOT NPs is vital for designing and producing these integrated NP systems successfully. This knowledge will enable researchers to tailor the properties of PEDOT NPs to meet specific application requirements, ultimately enhancing the efficacy of cancer theragnostic platforms.

This review aims to provide a comprehensive exploration of PEDOT NPs, examining their synthesis strategies, characterisation, and applications in cancer treatment. Firstly, we address common techniques for synthesising PEDOT NPs of varying size, morphology, and surface chemistry along with associated characterisation techniques. We also analyse recent advancements in using PEDOT NPs for electrostimulated drug delivery, and photothermal ablation of tumours. Finally, we discuss the current challenges and prospects for clinical translation. We aim that this review supports further efforts dedicated at exploring the potential of these nanosystems for more precise and personalised cancer nanomedicine.

2. Synthesis and characterisation of PEDOT NPs

Comprehending polymerisation processes, oxidative environments, and colloidal stabilisation strategies is essential to successfully synthesise PEDOT NPs. Important variables that impact the final NP size distribution, electrical conductivity through doping efficiency, and dispersion stability, include the choice of oxidant, type of surfactant, polymerisation temperature, reaction time, and post-processing steps. This section summarises different polymerisation techniques and the use of various oxidants and stabilisers to synthesise PEDOT NPs, while discussing the advantages and disadvantages of each strategy.


2.1. Synthesis approaches

Chemical oxidative polymerisation (using oxidant agents such as ferric chloride (FeCl_3) and ammonium persulfate ($(\text{NH}_4)_2\text{S}_2\text{O}_8$, APS)) or electrochemical polymerisation (applying an oxidising potential through electrodes, where polymers deposit on the working electrode) are the two methods that can be used for generating CPs.²¹ Generally, electrochemical polymerisation is employed to fabricate CP films, as this method needs a solid conductive surface where the polymerisation can take place, resulting in a homogeneous layer of polymer. Regarding CP NPs, particularly PEDOT NPs, oxidants like FeCl_3 and APS in aqueous medium are usually employed to induce oxidation and radical cation formation of EDOT (3,4-ethylenedioxythiophene). These radicals form dimers that subsequently get deprotonated. The oxidants initiate polymerisation into PEDOT chains, while contributing chloride (from FeCl_3) or sulphate





Additionally, CPs can be synthesised by template-based and template-free approaches. When using hard template techniques, polymer nanostructures are created using moulds. Applying this method to NP synthesis, the polymer is precipitated or polymerised on the surface of the template, resulting in a core-shell structure. Hollow CP NPs can be obtained by removing the template. Gold,⁵⁰ silica,^{51,52} and polystyrene NPs⁵³⁻⁵⁵ are some of the templates that have already been used to synthesise these nanostructures. Despite the fact that this technique is expected to give better control on the size and colloidal stability than soft templates, it has drawbacks, including the need for post-processing to eliminate the original template, which may have an impact on the nanostructures that are created, and the fact that this technique is too feeble for large-scale manufacturing.^{56,57}

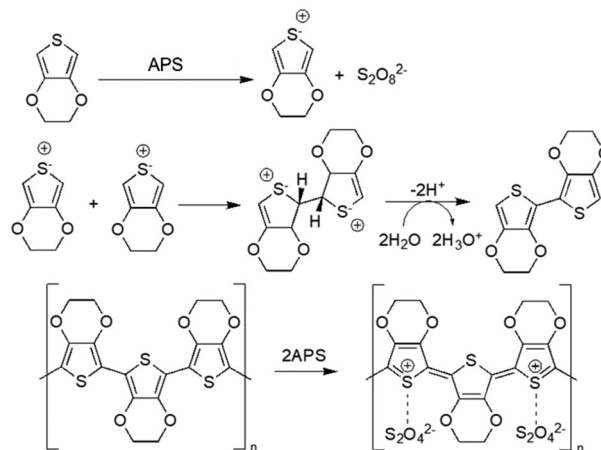

© 2024 The Author(s). Published by the Royal Society of Chemistry

Firstly, seed polymerisation was used as a synthetic method to generate PEDOT NPs, using a hard template as seed particles that will serve as polymerisation nuclei. Using this approach, Armes and coworkers described the synthesis of PEDOT-coated poly(*N*-vinylpyrrolidone)-stabilised polystyrene (PVP-stabilised PS) latex particles.⁵³ EDOT was polymerised in an aqueous solution using iron(III) tris(*p*-toluenesulfonate) (Fe(OTs)₃) at 85 °C. This methodology has the disadvantage of needing high temperature for the polymerisation to occur, and also the use of iron is a debatable disadvantage as it may lead to cytotoxic effects. Other studies also synthesised PEDOT NPs with the assistance of hard templates, namely PS and silica particles.^{52,55} The use of PEDOT as a coating on several metallic NPs has already been extensively reviewed elsewhere,⁷⁶ therefore, it will not be discussed in this review.

Table 1 Synthesis methods, reaction parameters, and resulting properties of PEDOT NPs reported in the literature from 2002 to 2023

Abbreviations: AOT – sodium bis(2-ethylhexyl)sulfosuccinate; CL-PSS – cross-linked PSS; DBSA – dodecyl benzenesulfonic acid; (Fe(OTs)₃) – iron(III) *p*-toluenesulfonate; H₂O₂ – hydrogen peroxide; o.n. – overnight; PEO – poly(ethylene oxide); PI-*b*-PMMA – polyisoprene-*block*-poly(methyl methacrylate); PSS-*co*-MA – PSS-*co*-(maleic acid); RT – room temperature; SDBS – sodium dodecyl benzenesulfonate; SDS – sodium dodecyl sulfate. ^a No surfactant used. ^b N/A: Not available or not reported in the referenced study.

In a different study, spherical PEDOT NPs were synthesised in a methanol/water solution using poly(ethylene oxide) end-functionalised with an EDOT moiety (α -EDOT-PEO) as a reactive stabiliser, and APS or iron(III) *p*-toluenesulfonate hexahydrate ($\text{Fe}(\text{OTs})_3 \cdot 6\text{H}_2\text{O}$) as oxidants.⁶² Using APS as oxidant and 20–50 wt% stabiliser resulted in a yield of approximately 30% of

A) Synthesis of PEDOT NPs. The process starts with Cyclohexane, which is treated with PI-b-PMMA to form micelles. These micelles are then treated with Acetonitrile iron(III) chloride to form "nanoreactors". An emulsion of [Acetonitrile-Fe(III)] in Cyclohexane is then formed. This emulsion is treated with EDOT to form PEDOT NPs. The PEDOT NPs are then purified to yield PEDOT NPs.

B) Synthesis of PEDOT:PSS-co-MA colloids. The process starts with EDOT + hexane + DBSA, which is treated with a spray gun (0.3 mm head) to form a micellar solution. This solution is then treated with 1. polymerization and 2. purification to yield PEDOT:PSS-co-MA colloids. The colloids are then treated with H₂O to yield PEDOT:PSS-co-MA colloids.

C) Redox reactions involved in the synthesis of PEDOT:PSS-co-MA colloids. The diagram shows the oxidation of EDOT to PEDOT by Fe³⁺ (oxidant 1) and H₂O₂ (oxidant 2). The reactions are as follows:

$$\text{EDOT} \xrightarrow{\text{Fe}^{3+}} \text{PEDOT} + \text{Fe}^{2+}$$

$$\text{EDOT} \xrightarrow{\text{H}_2\text{O}_2} \text{PEDOT} + \text{H}_2\text{O}$$

The diagram also shows the reduction of Fe³⁺ to Fe²⁺ by H₂O₂ and the subsequent oxidation of Fe²⁺ to Fe³⁺ by H₂O₂.

© 2024 The Author(s). Published by the Royal Society of Chemistry

PEDOT NPs after 72 h of reaction at room temperature (RT). Employing this method, highly spherical NPs with sizes ranging from 100 to 500 nm and conductivity up to $1.5 \times 10^{-2} \text{ S cm}^{-1}$ were successfully synthesised. The resulting NPs exhibited a significant improvement in colloidal stability compared to the NPs obtained in previous studies.

In another soft template approach, Zheng *et al.*⁶³ prepared PEDOT NPs by a reverse micelle method, also called water-in-oil emulsion, consisting of nanosised water droplets stabilised by surfactants in an oil phase.⁷⁸ An oxidant active point was formed at the reversed micelle's interface by mixing sodium bis(2-ethylhexyl)sulfosuccinate (AOT) with FeCl_3 , and the polymerisation reaction lasted 12 h at RT. The synthesised PEDOT NPs presented an electrical conductivity of 16.7 to 33.7 S cm^{-1} with particle sizes ranging from 30 to 100 nm. The dispersity of NP size shows the lack of control of particle sizes during synthesis, thus resulting in variability of results.

A novel spray emulsion polymerisation (SEP) technique was introduced by Han *et al.* to synthesise PEDOT NPs with the presence or absence of PSS-co-(maleic acid) (PSS-co-MA).⁶⁴ An EDOT/DBSA/hexane solution was sprayed, using a spray gun, into an aqueous solution containing FeCl_3 oxidant and PSS-co-MA, in the case of PEDOT:PSS-co-MA NPs (Fig. 3B). The functional groups of PSS-co-MA acted as oxidative polymerisation sites, dopants, and stabilisers of the core/shell morphology. Noncovalent interactions occurred between PSS-co-MA and PEDOT thiophene rings, with the polymerisation occurring within a few seconds, followed by magnetic stirring and posterior evaporation of the solvents. The resulting PEDOT and PEDOT:PSS-co-MA NPs exhibited sizes ranging from 100 to 200 nm, and conductivities of 3.2 and 0.29 S cm^{-1} , respectively. This discrepancy indicates that PSS-co-MA created a shell around the PEDOT core, obstructing charge hopping between neighbouring particles and lowering the conductivity of the PEDOT:PSS-co-MA composite. This technique generated well-distributed aqueous-dispersible PEDOT NPs, where the stabiliser, PSS-co-MA, was essential in improving their water-solubility. Inspired by this work, Tania Betancourt's group synthesised PEDOT:PSS-co-MA NPs using a similar two-surfactant emulsion polymerisation method.^{65–67} The differences in the protocol concern the organic phase, where EDOT and DBSA were dissolved in chloroform instead of hexane, added dropwise to the aqueous phase containing PSS-co-MA, and only then the FeCl_3 solution was added to the reaction mixture. The polymerisation lasted 1 h, upon stirring.

A different study used the bi-oxidant system, $\text{Fe}(\text{OTs})_3$ and hydrogen peroxide (H_2O_2), to synthesise PEDOT NPs by emulsion polymerisation.⁶⁸ It was rationalised that H_2O_2 's oxidative activity could restore Fe^{3+} (Fig. 3C). The cyclic oxidation–reduction process resulted in the sustained regeneration of these ions, oxidising more EDOT. The amount of iron salt added could be significantly reduced, conversion could be increased, and colloidal stability could be improved by adding this second oxidant, H_2O_2 . Sequential additions of $\text{Fe}(\text{OTs})_3$ and H_2O_2 resulted in stable PEDOT NPs with sizes of approximately 100 nm. Based on the same principle, a miniemulsion polymerisation approach was reported for the successful

synthesis of PEDOT NPs to investigate the function of the oxidising agents $\text{Fe}(\text{OTs})_3$ and H_2O_2 in particle synthesis efficiency and electrical properties.⁴⁷ EDOT was emulsified in an aqueous phase with the nonionic surfactant Lutensol AT 50. In one set of experiments, varying the EDOT/ $\text{Fe}(\text{OTs})_3$ ratio showed the conductivity increased with the increasing amount of $\text{Fe}(\text{OTs})_3$ being used as oxidiser. In a second set, keeping 1 : 1 EDOT/ $\text{Fe}(\text{OTs})_3$ ratio constant, adding H_2O_2 after $\text{Fe}(\text{OTs})_3$ led to much more stable macroscopic dispersions and spherical NP morphology stable for months. Conversely, increasing H_2O_2 concentration decreased NPs' conductivity due to side reactions with PEDOT chains. According to the findings, dispersions of approximately 30 nm PEDOT NPs with conductivities ranging from 2.1×10^{-6} to 2.6 S cm^{-1} could be achieved by adjusting the oxidant levels.

Paradee *et al.* studied the effects of oxidant concentration and surfactant type and concentration in the chemical oxidation polymerisation synthesis of PEDOT NPs.⁴⁹ APS was used as the oxidising agent and DBSA or sodium dodecyl sulfate (SDS) as surfactants. Depending on the polymerisation conditions, different NP morphologies (plum, globular, orange-peel, coralliform, raspberry agglomerate, and irregular), sizes (60 to 900 nm) and electrical conductivities (<1 to 153 S cm^{-1}) were obtained. Without surfactants, increasing APS concentration (from 0.15 M to 0.30 M) decreased particle size (from 212 to 70 nm) and increased conductivity (from 7.65 to 153.72 S cm^{-1}). The smallest sizes and highest conductivity occurred without the presence of surfactants, which can be explained by the quantum size effect and fewer blocking surfactant aliphatic segments. DBSA and SDS surfactants facilitated morphology control but reduced conductivity.

Building upon these findings, as PEDOT NPs with diverse morphologies were obtained, Wailes *et al.* adapted these water-based protocols to synthesise PEDOT nanofibres (NF) and nanospheres (NS).⁷⁹ This time, FeCl_3 was used as an oxidant, and the shape and size of the NPs were controlled by the interaction between the surfactant (SDS) and the oxidant concentrations (FeCl_3), as well as physical factors such as sonication or stirring during the synthesis process. As the concentration of FeCl_3 increased, the particles became less reliant on one another for stability, while increasing surfactant concentrations favoured the production of fibres. Nonetheless, NS formed at very high surfactant concentrations. One important factor in determining the NPs' morphology is the ratio of SDS to FeCl_3 . SDS : FeCl_3 ratios of around 2 were required for fibre formation, whereas ratios of around 3 were needed for longer and more dispersed fibres. Significantly higher ratios encouraged the formation of spherical NPs.

Using SDBS as a surfactant and $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ as an oxidant, Zhou's group used a hydrothermal synthesis to create well-dispersed PEDOT NPs with an approximate diameter of 17.2 nm.^{69,70} EDOT's solubility in the dispersion medium was controlled using a mixture of deionised water, methanol, and H_2SO_4 .

Moreover, through oxidative polymerisation of EDOT in the presence of cross-linked PSS (CL-PSS) as stabiliser and dopant,



2.1.2. Electrochemical polymerisation. To the best of our knowledge, the use of electropolymerisation, as a method for the synthesis of PEDOT NPs was only reported by Lee *et al.*⁷⁵ In this new approach, EDOT was confined in dichloromethane emulsion droplets dispersed in an aqueous solution. It was then within these droplets that the oxidative electropolymerisation of EDOT occurred, as they collided with the electrode at a potential of 1.15 V. Spherical PEDOT NPs with diameters of 200–650 nm were generated on the electrode surface, but the NPs could be dispersed in different solvents when ultrasonicated. Overall, this work offered a simple method for producing surfactant-free PEDOT NPs with a controlled morphology, although the diameters of the NPs were quite large and presented significant variability. The significant lack of literature on the electrochemical polymerisation of PEDOT NPs reveals a wide gap in research but may also expose the difficulties associated with controlling the NP size in this method.

The surface charge of NPs affects their interaction with biological membranes, cellular uptake, and biodistribution. Positively charged NPs demonstrate increased cellular uptake due to electrostatic interactions with negatively charged cell membranes. However, this can also lead to non-specific interactions and a higher immune response compared to neutral or negatively charged NPs.⁸⁵ Positively charged NPs are generally most rapidly cleared, followed by negatively charged NPs, while neutral and slightly negative NPs have the longest half-lives in circulation, because they can reduce protein adsorption.⁸ This phenomenon of non-specific adsorption of serum proteins forms a corona on the NP's surface, which can alter their physicochemical properties and reduce therapeutic efficacy. Specifically, studies report significantly larger amounts of

Table 2 Influence of characterisation parameters on therapeutic potential of PEDOT NPs

Parameter		Impact on therapeutic potential	Measurement techniques
Size	Smaller size (10–200 nm)	– Enhanced tumour penetration – Improved cellular uptake – Longer circulation time	– DLS – TEM – SEM
	Larger size (> 200 nm)	– Potential for faster clearance – Increased drug loading capacity	– DLS
Shape	Spherical	– Uniform cellular uptake	– TEM
	Rod-like	– Better margination – Enhanced tumour penetration – Higher protein corona formation	– SEM – AFM
Surface charge	Positive	– Increased cellular uptake – Potential for non-specific interactions	– Zeta potential measurement (DLS)
	Negative	– Longer circulation time – Reduced non-specific interactions	
	Neutral	– Reduced protein adsorption – Improved stealth properties	
Functionalisation	PEGylation	– Enhanced circulation stability and time – Reduced immunogenicity	– FTIR
	Targeting ligands	– Improved tumour-specific accumulation – Enhanced cellular internalisation	– XPS
	Stimuli-responsive moieties	– Controlled drug release – Improved therapeutic efficacy	– NMR
Thermal Stability	Higher stability	– Sustained performance during PTT – Improved safety profile	– TGA
Conductivity	Higher conductivity	– Enhanced photothermal conversion	– Four-point probe method
		– Improved potential for electrically-triggered drug delivery – Improved potential for electrotherapy	– Dielectric spectroscopy

Abbreviations: AFM – atomic force microscopy; DLS – dynamic light scattering; FTIR – Fourier-transform infrared spectroscopy; NMR – nuclear magnetic resonance; SEM – scanning electron microscopy; TEM – transmission electron microscopy; TGA – thermogravimetric analysis; XPS – X-ray photoelectron spectroscopy.

protein attaching on the rod-like particles compared to the spheres.⁸⁷

Functionalisation of PEDOT NPs offers opportunities to enhance their therapeutic potential. Surface modification of NPs with long-chain polymers such as polyethylene glycol (PEG) reduce the interactions with phagocytic cells of the RES, and minimise non-specific protein absorption onto the NP surface.⁸ Therefore, PEGylation increases the circulation time while shielding the NP surface from enzymes and antibodies that may prompt degradation, secretion and clearance.^{83,88} Addition of targeting ligands (*e.g.*, antibodies, peptides) can improve tumour-specific accumulation and cellular internalisation. Incorporating stimuli-responsive moieties (*e.g.*, pH-sensitive, redox-sensitive) enables controlled drug release and can significantly improve therapeutic efficacy.⁸

PEDOT NPs' thermal stability is important for PTT, ensuring that their structural integrity and performance is maintained for consistent therapeutic efficacy/safety. Conductivity, ultimately one of the main properties of PEDOT, is not only a significant factor for efficient photothermal conversion, but it is also essential for potential application of these NPs for electrically-driven drug delivery, as well as potential applications for electrotherapy, paving the way for dual-mode cancer therapies. Therefore, optimising these key parameters will be critical for PEDOT NPs' *in vivo* efficacy, versatility and overall effectiveness for cancer therapy, and thus should be taken into consideration for the design and synthesis of these NPs.

2.2.1. Morphological characterisation. The size, shape, diameter distribution, and degree of aggregation of NPs are crucial factors influencing their properties and usability. Hence, their characterisation holds fundamental significance. In the domain of NP morphological analysis, two primary methods are employed. The first approach entails several microscopy analyses, including transmission or scanning electron microscopy (TEM, SEM), and atomic force microscopy (AFM).⁸⁹ On one hand, SEM scans the surface of the dried and sputter-coated sample with high-energy electron beams and produces high resolution images with a scale down to the 10–20 nm range.⁹⁰ On the other hand, to obtain sub-nanometre imaging resolution, the preferred microscopy technique is TEM, which involves passing a focused electron beam through the NPs, which may just be dispersed on a grid, or may need more intensive preparation, such as be thinly sectioned or stained with heavy metal salts to enhance contrast. In TEM, the electron beam interacts differently with the NP core and its surrounding environment, creating a high-resolution detailed image. In a surface analysis technique, using a scanning probe tip and resolution that goes down to the nanoscale, AFM scans the surface topography. It can be applied to measure the surface roughness and visualise the surface texture of the material.⁹⁰

The second approach relates to NP stability in solution, thus, not requiring sample drying. Dynamic light scattering (DLS) is used to determine the hydrodynamic size of NPs in solution by measuring time-dependent fluctuations in



scattered light intensity.⁹¹ The obtained diameter values represent the particle and its surrounding solvent molecules, often yielding larger values due to this measurement. Due to its limitation in measuring the effective particle size, DLS serves mainly as a preliminary or reference method, often preceding microscopy examinations.

Regarding PEDOT NPs, studies in the literature focused mainly on the use of SEM/TEM and DLS to determine their diameters, which ranged between 30 and 400 nm, depending on the technique used. It was observed that, as expected, the diameter of the NPs determined by DLS was higher than that determined by SEM by approximately two-fold, as it can be seen in Table 1. The SEM and TEM images also allowed the visualisation of a typical spherical morphology of the PEDOT NPs in most studies.^{47,49,61,62,68,69,71,72,75} This implies that, in contrast to NPs with a rod-like shape, the great majority of NPs synthesised using the methods described above will exhibit less extravasation but less formation of protein corona when employed in *in vivo* experiments. Drug delivery studies using these NPs also reported an increase in the size of the loaded NPs due to the encapsulation of the drugs.^{20,22–27,73,92}

Paradee *et al.*⁴⁹ studied the effects of the oxidising agents and surfactants on the resultant PEDOT NPs sizes and morphologies. Based on this study and the results of the other studies discussed in Section 2.1, it is possible to state that increasing oxidant concentrations (particularly APS) lead to a decrease in the NP size. This effect is a result of the oxidising agent concentration having an impact on the initiation of the polymerisation and, consequently, leading to the formation of more active sites of the EDOT cations (Fig. 2). This leads to higher electro-repulsive forces between PEDOT polymeric cation radicals, and higher rate of polymerisation, thus resulting in smaller particle sizes.⁴⁹ Surfactant concentrations have an interesting effect on particle size because, at concentrations below the critical micelle concentration (CMC, 0.29×10^{-2} M), PEDOT NPs appear larger and in a globular form due to the lack of micelles. Smaller PEDOT particles are produced when polymerisation within the micelle core takes place at concentrations higher than the CMC. However, when the concentration of surfactant increases further, PEDOT particles agglomerate as a result of micellar fusion, producing PEDOT NPs that are larger in size and take the form of globular clusters.^{49,81} Overall, one can conclude that for achieving PEDOT NPs with optimal size, the selection of appropriate surfactant and reaction initiators are key parameters to take into consideration.

The zeta (ζ)-potential is a measure of the effective electric charge at the surface of the NPs, and quantifies the charge stability of the colloidal particles, providing information about their tendency to aggregate or to remain discrete.⁸⁹ In general, a ζ -potential above 25 mV (absolute value) indicates that the electrostatic repulsive forces exceed the attractive steric forces, implying colloidal stability, and the system is kept in a relatively stable dispersed state.²² The results of this measurement for the PEDOT NPs formulated in the studies listed in Table 1 and subsequent studies based on them revealed the synthesis of stable dispersed NPs in solution. Moreover, it is evident that

in most formulations the PEDOT NPs exhibit a negative surface charge.^{22,25–27,65–68,73} This negative charge is crucial for maintaining colloidal stability and effective biodistribution due to longer circulation time, as indicated by the influence of surface charge on therapeutic potential in Table 2. In the case of synthesis in a bi-organic medium, the NPs show a positive surface charge of +33 mV.⁷² This shift is likely due to the adsorption of positively charged ions or molecules from the bi-organic medium onto the surface of the NPs. The positive surface charge can influence interactions with biological membranes and cells, potentially enhancing cellular uptake, thus affecting the therapeutic potential as also summarised in Table 2.

2.2.2. Structural analysis. Chemical identification and assessment of PEDOT polymer chain structure relies on vibrational spectroscopies like Fourier-transform infrared (FTIR), Raman, and ultraviolet-visible (UV-Vis) spectroscopy.

FTIR spectroscopy involves irradiating the sample with infrared radiation ($12\,500$ to 10 cm^{-1}), with the absorbed radiation being converted into rotational or vibrational energy. FTIR is a crucial technique for chemical identification since it produces a spectrum with wavenumber that typically ranges from 4000 to 400 cm^{-1} , representing the molecular fingerprint of the sample.⁹³ Changes in the characteristic absorption band pattern point to a modification in the composition of the material. Thus, FTIR is particularly useful for confirming successful surface modifications.

In the FTIR spectrum of PEDOT NPs obtained using different synthesis conditions, key characteristic peaks corresponding to the PEDOT structure were observed. The vibrational bands around $1500\text{--}1400\text{ cm}^{-1}$ originated from the C–C or C=C stretching of the quinoidal structure of the thiophene ring and the stretching of the thiophene ring, respectively. Peaks from $1200\text{--}1000\text{ cm}^{-1}$ are associated with C–O–C vibrations of the ethyleneoxy groups. The peaks of the C–S bond in the thiophene ring were observed from $680\text{--}950\text{ cm}^{-1}$. Additional smaller peaks between 2800 to 3000 cm^{-1} were present when the NPs were obtained using a surfactant. These peaks correspond to the aliphatic C–H stretching mode depending on the long alkyl tail of the surfactant (*e.g.* DBSA).^{23,25,27,49,60,66,68,69,72,94} When using APS as oxidant, the presence of a peak around 1680 cm^{-1} indicates the presence of a carbonyl group, which is associated with a side reaction like overoxidation, since APS is a strong oxidant.⁴¹ Additionally, in PEDOT NPs formulated with H_2O_2 , a broad band in the range of $3300\text{--}3000\text{ cm}^{-1}$ is present, referable to the hydroxyl groups in the polymer chains.⁴⁷ FTIR can also be employed for confirming the success of the drug loading process on PEDOT NPs. For instance, the characteristic curcumin (CUR) bands, which are identified at 3506 cm^{-1} (OH), 1594 cm^{-1} (C=O) and 1269 cm^{-1} (enol C–O), were detected in the spectra of PEDOT/CUR NPs.²⁴ The spectra of PEDOT NPs loaded with pyrimethamine (PYR) presented the bands associated with both PEDOT NPs and free PYR, attributed to the $-\text{NH}_2$ group (3443 cm^{-1} and 3261 cm^{-1}) and the C=N group (between $1681\text{--}1409\text{ cm}^{-1}$) stretching vibration.²²

Raman relies on inelastic scattering of monochromatic light rather than mid-IR light absorption as in FTIR, and this



technique also identified characteristic ring and inter-ring vibrations in the range of 1500–500 cm^{-1} . Transition intensities provide indications of effective conjugation and doping levels.^{24,47,64,75} The Raman fingerprints of PEDOT NPs appear at 992 cm^{-1} , 1259 cm^{-1} , 1368 cm^{-1} , 1424 cm^{-1} and 1495 cm^{-1} , which have been related to the oxyethylene ring, $\text{C}_\alpha\text{--C}_\alpha'$ inter-ring stretching, $\text{C}_\beta\text{--C}_\beta$ stretching, symmetric $\text{C}_\alpha\text{=C}_\beta$ stretching and asymmetric $\text{C}_\alpha\text{=C}_\beta$ stretching vibrations, respectively.²⁴ Increasing the amount of neutral π -bonds in the polymer backbone results in a high Raman signal. Thus, higher doping levels induce more charge carriers that shield the overall Raman scattering efficiency, thus reducing Raman peak intensities in the spectrum. Additionally, the Raman bands exhibit a small downshift to lower energies as doping helps promote quinoid resonance forms.⁴⁷ For instance, Raman spectra of PEDOT NPs synthesised with different concentrations of $\text{Fe}(\text{OTs})_3$ showed no Raman signal at low $\text{Fe}(\text{OTs})_3$ concentrations, indicating a low polymerisation degree. At higher $\text{Fe}(\text{OTs})_3$ concentrations, the Raman signal decreases due to a higher doping level of the final material. Additionally, the intensity of the Raman signal decreases in the presence of H_2O_2 , corresponding to a reduction in the number of neutral π -bonds along the polymer backbone, and a shift in the signal related to asymmetric C=C stretching is observed. This shift indicates a decrease in electrical conductivity, attributed to changes in the conjugation of the PEDOT chains.⁴⁷

In UV-Vis spectroscopy, the intensity of a UV-Vis light beam is measured both before and after it passes through the sample, which is positioned between a light source and a photodetector. The sample's maximum absorption level determines the plotted wavelength.⁸⁹ The maximum absorption peak of PEDOT is in the 800–1000 nm range and is related to the polaronic and bipolaronic oxidised states. The peak position and intensity are positively correlated with the doping level of PEDOT. Generally, neutral PEDOT presents a broad absorption peak with lower intensity in the visible light region (400–600 nm), corresponding to the $\pi\text{--}\pi^*$ transition.^{22,23,47,66,72,73,75} Higher concentrations of $\text{Fe}(\text{OTs})_3$ cause an increase in absorption related to the polaronic and bipolaronic states (800–1000 nm), while lower concentrations cause an increase in absorption linked to the neutral π -bonds.⁴⁷ UV-Vis spectra of PEDOT NPs synthesised with varying volumes of H_2O_2 show high oxidation levels in the polymer chains, evidenced by the absorption of oxidised states. However, the absorption related to the conjugated neutral π -bond decreases with more H_2O_2 . This is likely because the radicals in the conjugated π -system interact with $\bullet\text{OH}$ radicals from H_2O_2 , bonding to the polymer backbone and breaking the conjugation, which significantly reduces electrical conductivity by hindering charge propagation along the polymer chains.⁴⁷

Moreover, UV-Vis spectroscopy is essential for characterising the optical properties of PEDOT NPs, which are crucial for their application in PTT. The absorption spectrum not only confirms the presence of PEDOT but also provides information on the NPs' ability to absorb light in the NIR region. This is explored in more detail in Section 3.1.

Complementary to the vibrational characterisation of the molecular structure, X-ray diffraction (XRD) provides information

on chain order, by evaluating the crystalline structure. This technique displays diffraction intensity over a range of angles, with peaks at specific 2θ values being related to lamellar sheet packing distances and $\pi\text{--}\pi$ interchain stacking distances.⁹⁵ The use of dopants and polymerisation conditions impact relative peak intensities and degree of crystallinity. The diffraction peaks of PEDOT NPs at 2θ of approximately 7° , 12° , and 18° correspond to a system in which the interchain packing is along a pseudo-orthorhombic a -axis. The sharper diffraction peak at 2θ of approximately 6° represents the interchain planar ring-stacking distance.^{49,60,64,72} Higher order in the PEDOT NP structure is induced by increasing the doping level with increasing oxidant concentration, namely APS. Additionally, the presence of surfactants reduces the degree of crystallinity of PEDOT NPs. Compared to PEDOT synthesised using DBSA, the diffraction peak of PEDOT generated using SDS is sharper. This effect is due to the bulky benzene ring structure of the DBSA causing PEDOT to have a more amorphous structure.^{49,66}

2.2.3. Surface chemistry. Focusing on the surface chemical composition and electronic state, X-ray photoelectron spectroscopy (XPS) provides elemental species ratios determined by measuring binding energies specific to each element.⁹⁶ The peaks obtained by this approach can be related to elements present in PEDOT.⁹⁷ Relative ratios of counterions like chlorine to sulphur (Cl/S) or oxygen to carbon (O/C) can quantify doping levels and oxidation state of PEDOT chains at NP surface, respectively. For instance, a higher Cl/S ratio indicates more doping of PEDOT NPs by the chlorine ions of FeCl_3 .⁷² Dopant identity can be confirmed from narrow scans over specific binding energy ranges. Additionally, XPS results can further support the successful loading of the NPs. In the case of PEDOT/PYR NPs, a nitrogen peak appears at 399.9 eV in the XPS spectrum, which is attributed to N–H and C–N from PYR.²²

While XPS measures the kinetic energy of electrons emitted from a sample during X-ray irradiation to characterise its composition, energy-dispersive X-ray (EDX) relies on the detection of X-rays emitted from the sample during electron beam bombardment, as it is performed in conjunction with SEM. XPS and EDX are complementary, but XPS provides additional chemical state information and is more surface-specific. Elemental analysis of NPs *via* EDX can confirm the presence of PEDOT elements (carbon, oxygen, sulphur). The degree of NP purification can also be determined by this analysis, since the absence of Fe, for instance in NPs made with FeCl_3 , suggests that Fe has been successfully removed from the NPs during purification.⁶⁶

2.2.4. Thermal stability. The thermal stability of PEDOT NPs can be characterised by thermogravimetric analysis (TGA) to provide their onset decomposition temperature ($T_{\text{d,onset}}$), a parameter correlated with thermal stability. This method monitors mass loss events as samples are heated in an inert gas atmosphere, usually N_2 . Initial mass loss below 150°C is attributed to the evaporation of residual solvents and stored moisture from the synthesis and washing steps, with a higher initial mass loss indicating a higher amount of trapped solvent.⁷² Moreover, if surfactants are used in the NPs



generates a depletion of the NPs electrical conductivity (from approximately 0.5 S cm^{-1} to approximately $5 \times 10^{-3} \text{ S cm}^{-1}$)⁴⁷

The unique properties of PEDOT NPs make them well-suited for a range of cancer therapy applications. In particular, the high NIR absorption and photothermal conversion efficiency enable their use in PTT. Additionally, PEDOT NPs can be developed as smart delivery systems for the targeted transport and delivery of chemotherapeutic drugs, owing to their facile surface modification and tuneable drug-loading capacity. A comprehensive overview of current developments in the use of PEDOT NPs in PTT and drug delivery approaches for cancer treatment is presented in this section (Table 3). We first address photothermal effects using PEDOT NP-based systems. Next, we highlight innovative PEDOT NP-based drug carriers designed for stimuli-responsive and targeted drug release.

Among alternative approaches, that could lessen the limitations currently attached to established cancer therapy, is hyperthermic therapy (HT). Hyperthermia is a state in which the body is exposed to high temperatures (often $>45\text{ }^{\circ}\text{C}$) and has been thoroughly researched in relation to cancer treatment since heat stress triggers the death of cancer cells.¹⁰⁶ HT has the potential to be used alone or in combination with radiation therapy or chemotherapy.¹⁰⁷ Localised hyperthermia triggered by NPs appears to be a promising strategy to treat cancer, since usual HT treatments are not tumour-focused, are invasive, and produce heat uniformly throughout the body,¹⁰⁸ which may result in adverse effects. Recently, PTT, which uses light as a stimulus for thermal therapy, has received a lot of attention. PTT therapy is based on an approach where light (typically NIR) is used to excite PTT agents, which in turn release energy as heat. NIR light, with wavelength between 700 and 900 nm, is the most common source of excitation due to its low attenuation and deep penetration in biological tissues.¹⁰⁹ PTT agents must fulfil some requirements, such as being dispersible in aqueous solutions; having a uniform shape and size (nanoscale); responding to NIR radiation; being sufficiently photostable to guarantee adequate diffusion time to reach tumours before losing their photosensitivity; and being biocompatible in living systems. CP NPs satisfy these conditions and have gained research interest due to their ability to be finely tuned to absorb NIR light, by chemically modifying the polymer backbone with functional groups or blended systems. The polymer chains also enable the coupling of drugs and biomarkers, allowing for applications like imaging and NIR-triggered drug delivery.^{110,111} To date, photothermal effects in cancer therapies have been described for PPy,^{112–120} PDA,^{121–130} PANI^{131–134} and PEDOT NPs, the latter being the focus of this review.

In 2012, Cheng *et al.* reported for the first time the use of PEDOT:PSS as an effective and safe organic PTT agent for

2.2.5. Electrical conductivity. Determining the electrical conductivity is crucial to understanding the electronic properties of PEDOT NPs. Conductivity measurements depend greatly on NP characteristics, like doping efficiency and PEDOT chain morphology. Common techniques include dielectric spectroscopy, which tracks changes in impedance under alternate current (AC) excitation to model conductivity contributions, two-point probe measurements, which apply low voltage to calculate resistance from the current response (direct current, DC), and four-point probe methods, which rely on the conversion of thin film sheet resistance to conductivity using separate pairs of current-carrying and voltage-sensing electrodes.⁹⁸ Comparing results from these techniques that directly quantify charge transport reveals how factors like crystallinity, dopant levels, and surfactant content impact conductivity. Therefore, reports on very high electrical conductivity (220 S cm^{-1}) of PEDOT NPs', measured by a four-point probe measurement, attribute this value to the PEDOT NPs' high doping level and uniform morphology.⁷² According to two-point probe measurements, higher concentrations of oxidant (APS) are associated with smaller NP sizes and high electrical conductivity (153 S cm^{-1} at 0.30 M APS).⁴⁹ Smaller particle size increases the maximal surface area for electron transport, and the doping level is also increased since more APS is used. Nevertheless, when the APS concentration is raised to levels that cause the NP size to rise, over-oxidation of the PEDOT NPs causes a decrease in electrical conductivity (0.29 S cm^{-1} at 0.60 M APS).⁴⁹ Consequently, this may be one of the reasons why the DBSA-APS system's conductivity is lower than that of the DBSA- FeCl_3 system.⁶⁰ Additionally, as surfactant concentrations increase, PEDOT NPs electrical conductivity decreases. The self-screening during polymerisation and the doping process *via* excessive dodecylbenzenesulfate anions of DBSA and dodecylsulfate anions of SDS are two factors contributing to this decrease, leading to conductivity values of $1.31 \times 10^{-2} \text{ S cm}^{-1}$ and $1.52 \times 10^{-2} \text{ S cm}^{-1}$, respectively.⁴⁹ Furthermore, compared to PEDOT NPs synthesised using SDS, the bulky benzene ring of the DBSA dopant leads to a steric barrier for electron movement in the PEDOT chain, reducing the electrical conductivity of PEDOT NPs.⁴⁹ Dielectric spectroscopy results indicated that PEDOT NPs' electrical conductivity increases (from 2.1×10^{-6} to 2.6 S cm^{-1}) with increasing Fe(OTs)_3 concentration (from 0.014 to 0.1 M), and that H_2O_2 (from 0 to 0.04 M) produces some change in the molecular structure of PEDOT that

Table 3 Summary of PEDOT-based NP systems for anticancer therapy

Anticancer therapy	Configuration of PEDOT NPs-based system	Cancer model	Ref.
PTT	PEGylated PEDOT:PSS NPs (PEDOT:PSS-PEG)	4T1 tumour-bearing mice (<i>in vivo</i>)	88
	PEDOT:PSS-PEG loaded with DOX, SN38, and Ce6	4T1 mice breast cancer cells (<i>in vitro</i>)	99
	PEDOT:PSS NPs	RKO and HCT116 colorectal cancer cells (<i>in vitro</i>)	100
	PEDOT NPs encapsulated in a nanogel	HCT116 cervical cancer cells (<i>in vitro</i>) and HCT116 tumour-bearing mice (<i>in vivo</i>)	70
	PEDOT:PSS NPs	MDA-MB-231 breast cancer cells (<i>in vitro</i>)	65
	PEDOT NPs	MDA-MB-231 breast cancer cells (<i>in vitro</i>)	66
	PEDOT NPs embedded in a dynamic thiol-Michael hydrogel	MDA-MB-231 breast cancer cells (<i>in vitro</i>)	67
	Magnetic NPs with PEDOT coating loaded with HCPT (Fe ₂ O ₃ @PEDOT-HCPT) ^a	4T1 breast, HeLa cervical cancer cells (<i>in vitro</i>) and 4T1 tumour-bearing mice (<i>in vivo</i>)	101
	Magnetic NPs with PEDOT:PSS coating (Fe ₃ O ₄ @PEDOT:PSS) ^a	MCF-7 tumour-bearing mice (<i>in vivo</i>)	102
	Magnetic NPs with PEDOT:PSS, Cyanine7, and 2-deoxyglucose-polyethylene glycol (MNP@PES-Cy7/2-DG) ^a	MCF-7 breast cancer cells (<i>in vitro</i>) and MCF-7 tumour-bearing mice (<i>in vivo</i>)	103
	Magnetic NPs with PEDOT coating loaded with siRNA (α-Fe ₂ O ₃ @PEDOT-siRNA) ^a	MCF-7 breast cancer cells (<i>in vitro</i>) and MCF-7 tumour-bearing mice (<i>in vivo</i>)	97
	PEDOT NPs loaded with CUR	PC3 prostate, MCF-7 breast cancer cells (<i>in vitro</i>) ^b	25
	PEDOT NPs and CUR loaded in poly(ε-caprolactone) (PCL) microfibres	MCF-7 breast cancer cells (<i>in vitro</i>) ^b	23
	PEDOT NPs and menadione integrated into a PGGA hydrogel	N/A	74
Electrostimulated drug delivery	PEDOT NPs loaded with fibrin-homing peptides (CREKA and CR(NMe)EKA)	PC3 prostate cancer cells (<i>in vitro</i>) ^b	73
	PEDOT NPs loaded with PYR	MG-63 osteosarcoma cells (<i>in vitro</i>) ^b	22
	PEDOT NPs loaded with CUR integrated into a PGGA hydrogel	N/A	24
	PEDOT NPs loaded with CAM integrated into a Alg-g-PAA hydrogel	HeLa cervical cancer cells (<i>in vitro</i>)	27
	PEDOT NPs loaded with CUR encapsulated inside coaxial poly(glycerol sebacate)/poly(caprolactone) (PGS/PCL) electrospun fibers	PC3 prostate, MCF-7 breast cancer cells (<i>in vitro</i>) ^b	104
	PEDOT NPs loaded with CR(NMe)EKA integrated into an injectable pH responsive phenylboronic acid grafted to chitosan (PBA-CS) hydrogel	MG-63 osteosarcoma, PC3 prostate cancer cells (<i>in vitro</i>) ^b	105

Abbreviations: Alg-g-PAA – poly(acrylic acid)-grafted sodium alginate; CAM – chloramphenicol; CUR – curcumin; Ce6 – chlorin e6; DOX – doxorubicin; HCPT – 10-hydroxycamptothecin; PES – phenylethynylsulfonamide; PGGA – poly(γ-glutamic acid); PIP – piperine; PYR – pyrimethamine; SN-38 – 7-ethyl-10-hydroxycamptothecin. ^a These studies use core-shell NPs with PEDOT shell. ^b In these studies, only the cytotoxicity of the drug loaded PEDOT NPs was assessed, and not the effect of applying electrical stimulation to the cells with the NPs.

in vivo cancer treatment.⁸⁸ The formulated PEDOT:PSS-PEG NPs were coated layer-by-layer with charged polymers before being conjugated with branched PEG, presenting a diameter of approximately 80 nm. The PEDOT:PSS-PEG NPs demonstrated high stability in a physiological environment, and a stealth-like behaviour following intravenous injection at a dose of 10 mg kg⁻¹ in Balb/c mice. Their long blood circulation half-life of 21.4 ± 3.1 h allowed for significant accumulation of the NPs at tumour sites due to the EPR effect. Thus, longer blood circulation and stealth nature were conferred by surface PEGylation. The potential of these PEDOT:PSS-PEG NPs to eliminate tumours *via* NIR-mediated photothermal ablation (808 nm laser irradiation with a power density of 0.5 W cm⁻² for 5 min) has been confirmed in experiments conducted on Balb/c mice bearing 4T1 tumours. Specifically, after laser irradiation, tumours on PEDOT:PSS-PEG-injected mice were completely eliminated one day post-irradiation, and these mice survived over 45 days without a single death. Furthermore, comprehensive blood tests and histological examination revealed no toxicity of the NPs to the treated mice within 40 days, indicating their safety profile at the tested dose (Fig. 4A).

Encouraged by these results, Gong *et al.*⁹⁹ conducted a follow-up study to further enhance the therapeutic potential of PEDOT:PSS-PEG NPs. Three aromatic medicinal compounds were loaded into the PEDOT:PSS-PEG NPs through π-π stacking

and hydrophobic interactions.⁹⁹ These molecules included the photosensitiser chlorin e6 (Ce6) and the chemotherapeutic medicines doxorubicin (DOX) and SN38. Remarkably, *in vitro* experiments with the 4T1 murine breast cancer cell line showed that loading the PEDOT:PSS-PEG NPs could enhance the solubility of water-insoluble drugs, such as SN38, while maintaining the drug's cytotoxicity. Furthermore, compared to free Ce6, Ce6-loaded NPs showed 5 to 6-fold higher cellular uptake and increased photodynamic therapy efficacy. Due to photothermal effects, DOX-loaded PEDOT:PSS-PEG NPs exposed to laser radiation (808 nm) resulted in a 5 times higher intracellular delivery of DOX. In comparison with individual treatments, the combination of laser and DOX-loaded NPs led to a substantial decrease in cancer cell viability and a synergistic effect on cancer cell death.

In another study involving PEGylation, Liu *et al.* reported the synthesis of PEDOT NPs with a size of 17.2 nm, and broad NIR absorption from 700–1250 nm.⁶⁹ The NPs were modified with PSS, indocyanine green (ICG) dye, PEG, and glutaraldehyde (GTA) to obtain PEDOT:ICG@PEG-GTA NPs. Under 1064 nm laser irradiation, the photothermal conversion efficiency was 71.1% and a temperature of 76.6 °C was reached, indicating excellent photothermal properties. *In vitro* studies showed the NPs had low toxicity in bacterial (*E. coli*, and *S. aureus*) and human cancer cell lines (U87MG glioblastoma cell line,



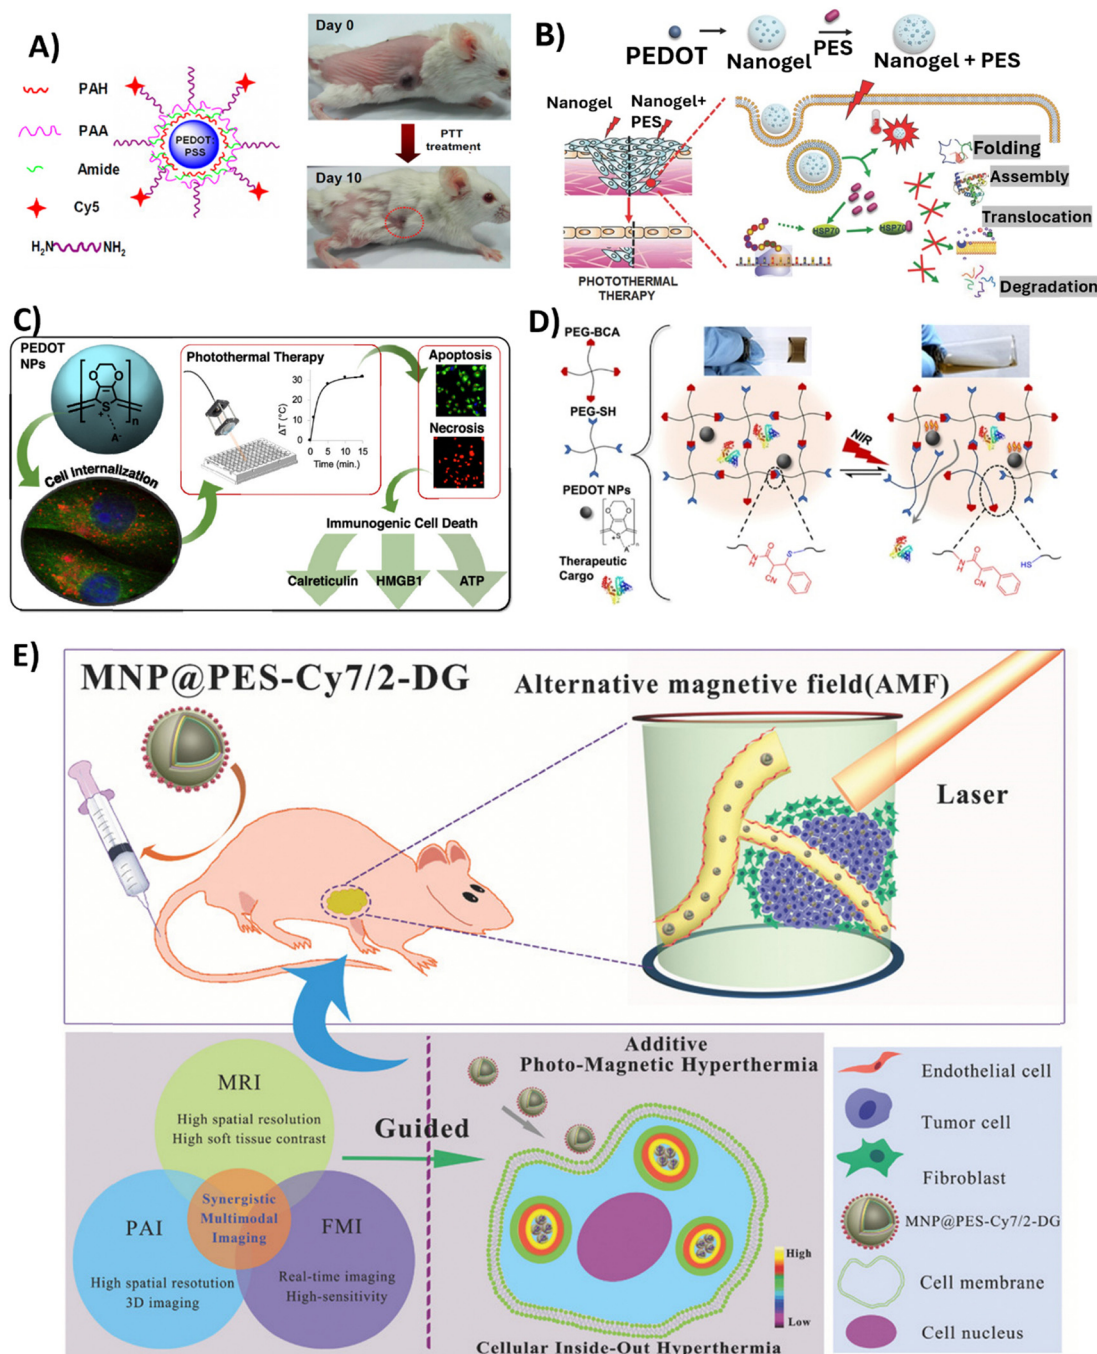


Fig. 4 Overview of the studies employing PEDOT NPs-based systems in anticancer PTT. (A) PEDOT:PSS-PEG NPs structure (left); Representative photos of a PEDOT:PSS-PEG-injected 4T1 tumour-bearing mouse at day 0 before PTT treatment and at day 10 after treatment. Complete tumour elimination was achieved after PTT treatment (right). Reproduced with permission from ref. 88. Copyright 2012 American Chemical Society. (B) Schematic illustrating Nanogel + PES synthesis for the PTT of deeper cancer cells by using PES that has been released to inhibit HSP70 function. Reproduced with permission from ref. 70. Copyright 2016 Wiley. (C) Schematic of the study developed by Huff *et al.* Reproduced with permission from ref. 66. Copyright 2020 American Chemical Society. (D) Schematic showing the cargo-loaded Gel/PEDOT system (dynamic thiol-Michael cross-linking between 4-arm PEG-BCA and 4-arm PEG-SH in the presence of PEDOT NPs and BSA-FITC or DOX), and the photothermally modulated release of the therapeutic cargo by NIR light. Reproduced with permission from ref. 67. Copyright 2020 American Chemical Society. (E) Diagram of intracellular photomagnetic hyperthermia guided by trimodality molecular imaging under intravenous administration of MNP@PES-Cy7/2-DG. Reproduced with permission from ref. 103. Copyright 2018 Wiley.

and HeLa cervical carcinoma cell line). By combining 808 nm and 1064 nm laser irradiation of NP-treated *E. coli* and *S. aureus*

bacterial strains resulted in approximately 99% cell death, demonstrating a synergistic photothermal and photodynamic



bactericidal effect. Although the effects of applying a PTT to the cancer cell lines used in this study have not been examined, the study's promising results point to the relevance of conducting such an experiment.

Other *in vitro* studies followed using PEDOT NPs as PTT agents. MacNeill *et al.* synthesised 100–200 nm size PEDOT:PSS NPs with elevated NIR absorption capacity.¹⁰⁰ Studies performed on RKO and HCT116 colorectal cancer cell lines revealed negligible toxicity of the NPs, and photothermal ablation resulted in approximately 20% cell survival after NIR irradiation. Interestingly, 200–400 nm diameter and 4–10 μm length PEDOT nanotubes (NTs) showed stronger NIR absorption, higher temperature increase upon irradiation in comparison with NPs, and photothermal ablation that resulted in <5% cell survival. Therefore, PEDOT NTs appear to be superior agents over NPs for PTT of cancer. Thus, modifying the aspect ratio from a spherical to a tubular/rod shape may potentially be an effective way to improve photothermal performance of PEDOT NPs.¹⁰⁰

Further works synthesised PEDOT:PSS-co-MA NPs with diameters <100 nm, strong NIR absorption (peak at 750 nm), high photothermal conversion efficiency of 53%, and significant photostability.⁶⁵ Studies conducted in MDA-MB-231 breast cancer cells demonstrated the cytocompatibility of the NPs and showed that the presence of the NPs at the highest concentration of 500 $\mu\text{g mL}^{-1}$ led to the ablation of approximately 80% of cancer cells upon 808 nm laser irradiation with a power density of 7 W cm^{-2} for 5 or 15 min intervals.

To improve the depth at which PTT is effective for cancer treatment, another group developed a nanocomposite platform containing 17.2 nm PEDOT NPs as a photothermal agent along with the heat shock protein 70 (HSP70) inhibitor, phenylethanesulfonamide (PES), encapsulated in a thermoresponsive poly(*N*-isopropylacrylamide-co-acrylic acid) (PNIPAM-co-AAc) polymer shell.⁷⁰ Upon NIR irradiation (808 nm, 0.1 W cm^{-2} for 10 min), the Nanogel + PES underwent a phase transition releasing PES to inhibit HSP70 function in HCT116 colon cancer cells and HCT116 tumour-bearing mice. In the latter case, Nanogel + PES with PEDOT NPs was administered at a dose of 10 mg kg^{-1} . This led to increased susceptibility to heat damage of cancer cells, as observed by the 2-fold increase in caspase-3 activity, and also led to an improvement in PTT depth effectiveness (Fig. 3B).

In 2020, Huff *et al.* developed PEDOT NPs to not only evaluate their potential as PTT agents, but also to investigate the causes of PTT-induced cell death.⁶⁶ Therapies such as PTT offer a means to heat targeted cancer cells to temperatures that lead to the release of damage-associated molecular patterns (DAMPs), which are the key signals required to activate dendritic cells and tumour-targeting T cells. Specific DAMPs like surface-exposed calreticulin and secreted high mobility group box 1 (HMGB1) serve as adjuvants to stimulate antigen-presenting cells and modulate a strong anti-tumour immune response. Thus, PTT offers opportunities not only for direct cancer cell death through hyperthermia, but also for activation of immunogenic cell death pathways. The synthesised spherical

PEDOT NPs, with a size of approximately 40 nm, presented the ability to strongly absorb NIR light between 700 and 900 nm. Upon irradiation with an 808 nm NIR laser at 3 W cm^{-2} , 10 to 500 $\mu\text{g mL}^{-1}$ of PEDOT NPs internalised in MDA-MB-231 cancer cells generated an increase in temperature of 32 $^{\circ}\text{C}$. This level of photothermal heating was adequate to induce cell death after 5–15 min of laser exposure. It was observed that the NPs caused cell death through apoptosis and necrosis, depending on the concentration and incubation time. Apoptosis was more prominent with shorter incubation times, while necrosis was more common with longer incubation times (6–24 h). In addition, the results of this study showed that the emergence of DAMPs was produced by PEDOT NP-mediated PTT. Particularly, cells subjected to higher heat doses showed increased calreticulin translocation to the cell membrane, increased cytosolic HMGB1, and decreased internal ATP. Therefore, PTT employing PEDOT NPs has the potential for the selective killing of cancer cells through immunogenic cell death (Fig. 3C).

In a very recently published study,⁶⁷ a dynamic thiol-Michael hydrogel with embedded PEDOT NPs was synthesised as a photothermally responsive material for controlled drug release,⁶⁷ taking advantage of hydrogels' capacity to absorb and retain a large amount of water and their tuneable characteristics and customisable manufacturing methods.¹³⁵ In this study, spherical PEDOT NPs with a diameter of 50 nm and NIR optical absorption were prepared *via* oxidative emulsion polymerisation and incorporated *in situ* during hydrogel formation. These PEDOT-composite hydrogels (Gel/PEDOT) underwent a reversible gel-to-solution transition at 45–50 $^{\circ}\text{C}$, which enabled thermoresponsive and NIR-laser-triggered release of the encapsulated model protein. For the release studies, bovine serum albumin labelled with fluorescein (BSA-FITC) was used, and pulsatile release was successfully demonstrated over 7 temperature cycles. Laser irradiation at 808 nm (2.65 W cm^{-2} , 15 min) induced photothermal heating of the PEDOT NPs to trigger BSA-FITC release on demand. The cytocompatibility of Gel/PEDOT was confirmed in both MDA-MB-231 breast cancer cells and 3T3 fibroblasts. Additionally, DOX could be encapsulated and laser-triggered released, retaining bioactivity to induce breast cancer cell death (Fig. 4D).

The properties of PEDOT that make it an effective PTT agent can be utilised not only in the form of PEDOT NPs, but also as a coating applied onto the surface (shell) of other NP cores. This allows both taking advantage of PEDOT's excellent properties for photothermal ablation and good biocompatibility, as well as the intrinsic functionality of the NP core for applications like imaging or drug delivery. Based on that, iron oxide (Fe_3O_4) NPs doped with 10-hydroxycamptothecin (HCPT) drug nanorods (NR) coated with PEDOT were developed.¹⁰¹ Upon irradiation with an 808 nm NIR laser at a power density of 1 W cm^{-2} for 10 min, the nanostructures showed excellent photothermal heating, reaching a temperature of 45 $^{\circ}\text{C}$. *In vitro* combination of chemotherapy and PTT led to less than 5% of 4T1 and HeLa cell viability. *In vivo* therapy studies involved intravenously injecting BALB/c mice bearing 4T1 tumours with the nanostructures at a dosage of 6 mg kg^{-1} , and the PTT regimen



PEDOT's capacity to respond to NIR, thus being a very promising PTT agent.

3.2. Electrically triggered drug delivery

To overcome the concerns related to currently administered chemotherapy, the development of new drug delivery strategies has been prompted. Particularly, the use of CP systems, including hydrogels, NPs, and nano- and microfibres, has shown the potential for delivering accurate dosages of drugs.^{20,136,137} Moreover, external stimuli have been used to trigger the delivery of drugs at specific locations and to control drug release rates. These stimuli can be endogenous (such as changes in pH, redox or enzymatic reactions) or exogenous (such as radiation, changes in temperature, ultrasounds, magnetic, and electric).¹⁰

Electroresponsive devices of polymeric structure have shown great promise for on-demand drug release, with the potential to be used in localised treatment through wireless controls. The oxidation–reduction properties of CPs interfere in the electrostatic forces that exist between the drug and the charged polymer, thus applying external voltages may promote the formation or disruption of drug-polymer interactions.²⁰ Furthermore, the electromechanical response of CPs allows for the intrinsic expansion and contraction of the polymers, which can be exploited to trigger the drug's mechanical release.^{23,138}

PEDOT has been widely utilised to load multiple drugs, including those used in cancer therapy, for subsequent controlled release by applying electrical stimulation.^{139,140}


Regarding the use of PEDOT NPs, Alemán's group has been focusing on these nanoplateforms for electrostimulated drug delivery of anticancer drugs. In an initial study, they investigated the controlled release of piperine (PIP) and curcumin (CUR) using PEDOT NPs as nanocarriers, with the drugs being loaded during emulsion polymerisation synthesis of NPs.²⁵ CUR is particularly interesting as it exhibits a broad range of therapeutic features, including anticancer, antiviral, antifungal, antibacterial, and anti-inflammatory properties.¹⁴¹ Kinetics experiments revealed a significantly slower, more gradual release profile for CUR compared to PIP from the NPs, suggesting that CUR and PEDOT NPs had stronger polymer-drug interactions. CUR release of up to 38% of the loaded drug was significantly increased when a negative voltage potential of -1.25 V was applied to CUR/PEDOT NPs for 3 min. In contrast, PIP release was not enhanced, indicating that PIP does not have strong interactions with PEDOT, but the interactions between CUR and PEDOT NPs were responsive to electrical control due to charge changes along the polymeric matrix disrupting the interactions between CUR and PEDOT. Human prostate adenocarcinoma (PC3) and breast adenocarcinoma (MCF-7) cancer cell lines were subjected to increasing concentrations of free CUR and CUR/PEDOT NPs for 24 h to assess the cytotoxicity of the treatment. As a whole, the study showed that the electroresponsive CUR/PEDOT NPs system exhibits potential for spatiotemporally-regulated dosage, which is valuable for CUR-based anticancer therapy. In a follow-up study, a hybrid system was developed by incorporating CUR/PEDOT into a poly(γ -glutamic acid) (PGGA) hydrogel.²⁴ The rationale was to leverage

Overall, the use of PEDOT NPs in PTT applications for cancer therapy appears to often involve stabilisation of the NPs with other polymer layers, with PSS and PEG being the most reported. Alternatively, encapsulation of PEDOT NPs within hydrogels, nanogels and polymeric shells appears to be an effective strategy. One can conclude that interactions with other polymeric matrices or chains do not appear to hinder



printed electrodes, instead of a conventional three-electrode system, allowing to design a more efficient system for the release of CUR from PEDOT NPs (65% of CUR release after applying a potential of -1.5 V for 180 s). Additionally, a wireless electrostimulation platform using these CUR/PEDOT NPs encapsulated inside coaxial poly(glycerol sebacate)/PCL (PGS/PCL) electrospun fibres was set up which promoted a decrease of 67% in cancer cell viability.¹⁰⁴

Another study developed 35–47 nm PEDOT NPs to load and achieve controlled, electrically-triggered release of the fibrin-targeting peptides Cys-Arg-Glu-Lys-Ala (CREKA) and CR(NMe)EKA. The latter being a CREKA analogue with enhanced peptide resistance against proteolysis, which is one of the major limitations of therapeutic peptide delivery.⁷³ These pentapeptides interact with fibrin clots and have high targeting ability to fibrin–fibronectin complexes in animal tumour models, and these can be employed in cancer diagnosis and treatments.¹⁴⁴ The results of the study showed that PC3 prostate cancer cells were more susceptible to peptide-loaded particles than healthy cells. Applying cyclic voltammetry electrical stimuli to peptide-loaded NPs caused significantly increased peptide release (up to 38% release after 100 cycles), when compared to absence of stimulation. The mechanism of peptide release can be explained by peptide–PEDOT interactions becoming weaker when polymer chains are reduced and oxidised by an external voltage (Fig. 5B). In a subsequent study,¹⁰⁵ the group found that after loading CR(NMe)EKA/PEDOT NPs into an injectable pH responsive hydrogel, formed by phenylboronic acid grafted to chitosan (PBA-CS), the efficiency of the controlled peptide release increases approximately by a factor of 2.6.

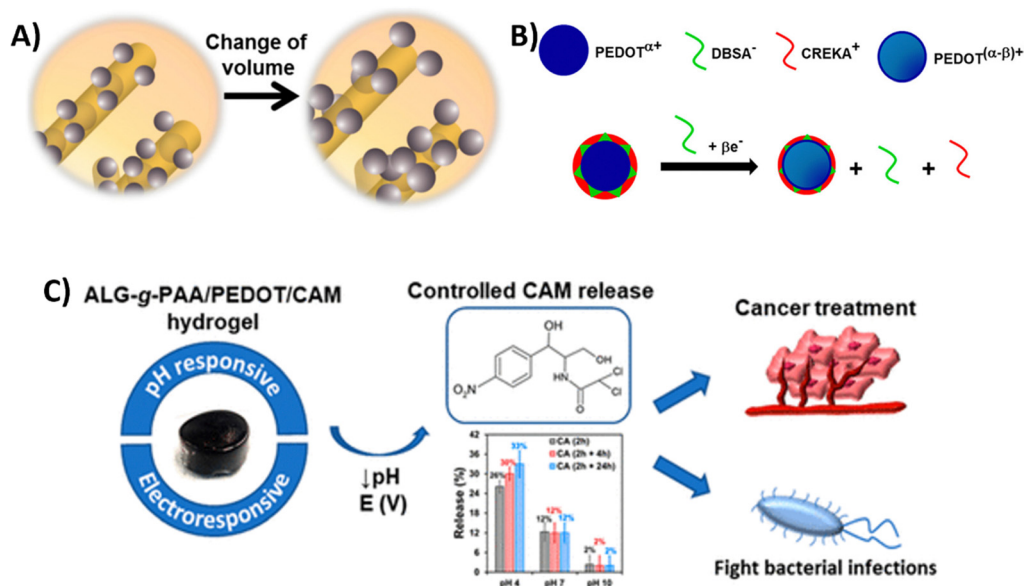

Mater. Adv., 2024, 5, 7561–7583 | 7577

for patients. Additionally, the integration of PEDOT NPs into other stimuli-responsive systems allows for a very highly controlled drug release, which is of utmost importance in cancer therapy.

Integrating PEDOT NPs coated with anodically polymerised poly(hydroxymethyl-3,4-ethylenedioxythiophene) (PHMeEDOT) chains into a (PGGA) biohydrogel allowed for the development of a vitamin K3 (or menadione) release system that could monitor the concentration of the drug being administered.⁷⁴ Vitamin K3 molecules organised in shells surrounding PEDOT NPs agglomerates when the drug was added to the initial gelling solution, and were gradually released to a physiological medium. With vitamin K3 acting as the active principle in many diseases, including cancer,¹¹⁷ this integrated system holds great promise for the creation of theragnostic treatment systems.¹⁴⁶

4. Challenges in the clinical application of PEDOT NPs & future directions

Regarding the biological part, understanding the pharmacokinetics (absorption, distribution, metabolism, and excretion) of the NPs as well as evaluating systemic toxicity and immunotoxicity are crucial to ensure that the NPs do not harm the overall health of the patient and do not cause inflammation or immunosuppression.¹⁰ Controlling the fate of PEDOT NPs *in vivo* remains difficult. While attempts have been made to modulate NPs to increase circulation time and tumour retention, risks of accumulation-related toxicity in liver, lungs, and kidneys persist.¹¹ To address this challenge, future studies should explore biodegradable PEDOT formulations. Moreover, aggregation in biological fluids alters NP physicochemical properties and reduces therapeutic efficacy. Also, protein corona formation leads to uptake of the NPs by the mononuclear phagocytic system, which must be avoided.^{11,12} Developing stealth PEDOT NPs with reduced protein adsorption and improved stability in biological fluids represents a key area for future research.

Technological challenges include scale-up synthesis, forecasting clinical performance based on preclinical data and achieving scalable production of NPs verified by Good Manufacturing Practices (GMP). Clinical performance is further impacted by study design weaknesses, such as small sample sizes, and overreliance on animal models that do not translate effectively to humans.^{11,151}

Overall, we can conclude that PEDOT NPs are very versatile in terms of the choice of anticancer drug to be loaded into the particles, as seen from the wide variety of drugs discussed, from small molecules to peptides. It is also important to note that the diversity of electrostimulation techniques deals with voltages, that are safe for the human body, lowering potential risks

Therefore, interdisciplinary teamwork between researchers, clinicians, engineers and regulators, and the use of computational models and advanced preclinical technologies, rewards addressing biological, technological and regulatory challenges, thus improving the clinical translation of the use of PEDOT NPs for therapeutics against cancer.

The considerable potential of PEDOT NPs to serve as versatile anticancer theragnostic agents has been discussed in this review. We have outlined common techniques for synthesising NPs with size, morphology, electrical conductivity, and surface chemistry that are tailored by adjusting the temperature, reaction time, stabilisers, and oxidants. Furthermore, extensive structural, electrochemical, and thermal characterisation relates synthetic conditions to resultant NP behaviour and characteristics. Particularly, PEDOT NPs exhibit efficient NIR absorption and photothermal conversion, making them useful for targeted, minimally invasive tumour photothermal ablation. Electrical stimulation for triggering the on-demand release of therapeutic agents is further facilitated by their intrinsic conductivity and electrochemical activity.

PEDOT NP-based platforms that combine drug delivery, photothermal heating, and imaging with temporal and spatial control have been designed in recent research. The potential of these nanosystems to concentrate in tumours, induce highly localised hyperthermia under NIR irradiation, and deliver anticancer drugs in response to electrical stimuli is confirmed by *in vitro* and *in vivo* research. Researchers must continue to systematically examine how slight modifications to the engineering of PEDOT NPs may affect therapeutic efficacy. The development of smart anticancer nanotheragnostics will be fuelled by the optimisation of synthesis procedures in conjunction with cytotoxicity testing and preclinical models. By addressing remaining problems in an interdisciplinary and cooperative manner, PEDOT NPs can fulfil their therapeutic potential and revolutionise cancer treatment.

We believe that our thorough examination of the fundamental concepts behind the synthesis, properties, and anticancer applications of PEDOT NPs has assisted in clearly illustrating these systems as powerful tools for personalised cancer nanomedicine. Future innovation should therefore concentrate on customising NP design for these highly tailored and targeted therapeutic modalities.

Author contributions

This review was conceptualised by FF, PS-A and TE. DD contributed to writing original draft. LR, FF, PS-A and TE contributed to the review and editing of this manuscript.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Conflicts of interest

The authors declare no conflicts of interest.

Acknowledgements

The authors acknowledge funding from FCT—Portuguese Foundation for Science and Technology (FCT/MCTES), with dedicated funding from the project eOnco (2022.07252.PTDC), the PhD scholarship (SFRH/BD/145057/2019) and also through institutional funds to iBB (UIDB/04565/2020 and UIDP/04565/2020) and Associate Laboratory i4HB (LA/P/0140/2020). This project also received financial support from “la Caixa” Foundation (ID 100010434) LCF/BQ/PI22/11910025.

References

- ## Data availability
- No primary research results, software or code have been included and no new data were generated or analysed as part of this review.
- ## Conflicts of interest
- The authors declare no conflicts of interest.
- ## Acknowledgements
- The authors acknowledge funding from FCT—Portuguese Foundation for Science and Technology (FCT/MCTES), with dedicated funding from the project eOnco (2022.07252.PTDC), the PhD scholarship (SFRH/BD/145057/2019) and also through institutional funds to iBB (UIDB/04565/2020 and UIDP/04565/2020) and Associate Laboratory i4HB (LA/P/0140/2020). This project also received financial support from “la Caixa” Foundation (ID 100010434) LCF/BQ/PI22/11910025.
- ## References
- 1 H. Sung, J. Ferlay, R. L. Siegel, M. Laversanne, I. Soerjomataram, A. Jemal and F. Bray, *Ca-Cancer J. Clin.*, 2021, **71**, 209–249.
 - 2 L. Sapio and S. Naviglio, *Int. J. Mol. Sci.*, 2022, **23**, 5296.
 - 3 K. Nurgali, J. A. Rudd, H. Was and R. Abalo, *Front. Pharmacol.*, 2022, **13**, 1007762.
 - 4 R. Baghban, L. Roshangar, R. Jahanban-Esfahlan, K. Seidi, A. Ebrahimi-Kalan, M. Jaymand, S. Kolahian, T. Javaheri and P. Zare, *Cell Commun. Signaling*, 2020, **18**, 59.
 - 5 J. Shi, A. R. Votruba, O. C. Farokhzad and R. Langer, *Nano Lett.*, 2010, **10**, 3223–3230.
 - 6 M. Dessale, G. Mengistu and H. M. Mengist, *Int. J. Nanomed.*, 2022, **17**, 3735–3749.
 - 7 Y. Zheng, L. Michalek, Q. Liu, Y. Wu, H. Kim, P. Sayavong, W. Yu, D. Zhong, C. Zhao, Z. Yu, J. A. Chiong, H. Gong, X. Ji, D. Liu, S. Zhang, N. Prine, Z. Zhang, W. Wang, J. B.-H. Tok, X. Gu, Y. Cui, J. Kang and Z. Bao, *Nat. Nanotechnol.*, 2023, **18**, 1175–1184.
 - 8 M. J. Mitchell, M. M. Billingsley, R. M. Haley, M. E. Wechsler, N. A. Peppas and R. Langer, *Nat. Rev. Drug Discovery*, 2021, **20**, 101–124.
 - 9 J. Yin, S. Wang, T. Tat and J. Chen, *Nature Rev. Bioeng.*, 2024, **2**, 541–558.
 - 10 L. Sun, H. Liu, Y. Ye, Y. Lei, R. Islam, S. Tan, R. Tong, Y. B. Miao and L. Cai, *Signal Transduction Targeted Ther.*, 2023, **8**.
 - 11 S. Gavas, S. Quazi and T. M. Karpiński, *Nanoscale Res. Lett.*, 2021, **16**, 173.
 - 12 J. Baranwal, B. Barse, A. Di Petrillo, G. Gatto, L. Pilia and A. Kumar, *Materials*, 2023, **16**, 5354.
 - 13 N. Bertrand, J. Wu, X. Xu, N. Kamaly and O. C. Farokhzad, *Adv. Drug Delivery Rev.*, 2014, **66**, 2–25.
 - 14 J. Wu, *J. Pers. Med.*, 2021, **11**, 771.
 - 15 J. Shi, P. W. Kantoff, R. Weoster and O. C. Farokhzad, *Nat. Rev. Cancer*, 2017, **17**, 20–37.
 - 16 R. Zeineldin and J. Syoufji, 2017, pp. 3–12.
 - 17 T.-H. Le, Y. Kim and H. Yoon, *Polymers*, 2017, **9**, 150.
 - 18 K. Namsheer and C. S. Rout, *RSC Adv.*, 2021, **11**, 5659–5697.
 - 19 J. Torras, J. Casanovas and C. Alemán, *J. Phys. Chem. A*, 2012, **116**, 7571–7583.
 - 20 A. Puiggali-Jou, L. J. del Valle and C. Alemán, *J. Controlled Release*, 2019, **309**, 244–264.
 - 21 Z. Rahimzadeh, S. M. Naghib, Y. Zare and K. Y. Rhee, *J. Mater. Sci.*, 2020, **55**, 7575–7611.
 - 22 H. Enshaei, A. Puiggali-Jou, N. Saperas and C. Alemán, *Soft Matter*, 2021, **17**, 3314–3321.
 - 23 A. Puiggali-Jou, A. Cejudo, L. J. Del Valle and C. Alemán, *ACS Appl. Bio Mater.*, 2018, **1**, 1594–1605.
 - 24 H. Enshaei, B. G. Molina, A. Puiggali-Jou, N. Saperas and C. Alemán, *Eur. Polym. J.*, 2022, **173**, 111199.
 - 25 A. Puiggali-Jou, P. Micheletti, F. Estrany, L. J. del Valle and C. Alemán, *Adv. Healthcare Mater.*, 2017, **6**, 1700453.
 - 26 H. Enshaei, A. Puiggali-Jou, L. J. del Valle, P. Turon, N. Saperas and C. Alemán, *Adv. Healthcare Mater.*, 2021, **10**, 2001636.
 - 27 L. Resina, K. El Hauadi, J. Sans, T. Esteves, F. C. Ferreira, M. M. Pérez-Madrigal and C. Alemán, *Biomacromolecules*, 2023, **24**, 1432–1444.
 - 28 C. Boehler, Z. Aqrave and M. Asplund, *Bioelectron. Med.*, 2019, **2**, 89–99.
 - 29 N. Gao, J. Yu, Q. Tian, J. Shi, M. Zhang, S. Chen and L. Zang, *Chemosensors*, 2021, **9**, 79.
 - 30 S. Střiteský, A. Marková, J. Vítěček, E. Šafaříková, M. Hrabal, L. Kubáč, L. Kubala, M. Weiter and M. Vala, *J. Biomed. Mater. Res., Part A*, 2018, **106**, 1121–1128.
 - 31 S. Ummartyotin, J. Juntaro, C. Wu, M. Sain and H. Manuspiya, *J. Nanomater.*, 2011, **2011**, 1–7.
 - 32 M. F. F. das Neves, J. P. V. Damasceno, O. D. L. Junior, A. J. G. Zarbin and L. S. Roman, *Synth. Met.*, 2021, **272**, 116657.
 - 33 Z. Liu, B. Lu, Y. Gao, T. Yang, R. Yue, J. Xu and L. Gao, *RSC Adv.*, 2016, **6**, 89157–89166.
 - 34 R. Madhuvilakku, S. Alagar, R. Mariappan and S. Piraman, *Anal. Chim. Acta*, 2020, **1093**, 93–105.
 - 35 B. G. Molina, L. J. del Valle, P. Turon, E. Armelin and C. Alemán, *J. Phys. Chem. C*, 2019, **123**, 22181–22190.
 - 36 V. Chellappa, J. Annaraj and S. Suresh, *Mater. Chem. Phys.*, 2024, **319**, 129330.
 - 37 J. W. Park, W. Na and J. Jang, *J. Mater. Chem. A*, 2016, **4**, 8263–8271.
 - 38 I. Adam-Cervera, J. Huerta-Recasens, C. M. Gómez, M. Culebras and R. Muñoz-Espí, *Polymers*, 2023, **16**, 100.
 - 39 M. Rajesh, C. J. Raj, B. C. Kim, R. Manikandan, S.-J. Kim, S. Y. Park, K. Lee and K. H. Yu, *RSC Adv.*, 2016, **6**, 110433–110443.
 - 40 A. Serafin, M. C. Rubio, M. Carsi, P. Ortiz-Serna, M. J. Sanchis, A. K. Garg, J. M. Oliveira, J. Koffler and M. N. Collins, *Biomater. Res.*, 2022, **26**, 63.
 - 41 Y. Han, M. Sun, X. Lu, K. Xu, M. Yu, H. Yang and J. Yin, *Composites, Part B*, 2024, **273**, 111241.

- Mater. Adv., 2024, 5, 7561–7583 | 7581

- 93 F. Huth, A. Govyadinov, S. Amarie, W. Nuansing, F. Keilmann and R. Hillenbrand, *Nano Lett.*, 2012, **12**, 3973–3978.
- 94 C. Kvarnström, H. Neugebauer, S. Blomquist, H. J. Ahonen, J. Kankare and A. Ivaska, *Electrochim. Acta*, 1999, **44**, 2739–2750.
- 95 B. Ingham, *Crystallogr. Rev.*, 2015, **21**, 229–303.
- 96 E. Korin, N. Froumin and S. Cohen, *ACS Biomater. Sci. Eng.*, 2017, **3**, 882–889.
- 97 A. H. Odda, T. Y. Cheang, H. F. Alesary, L. Liu, X. Qian, N. Ullah, G. Wang, Y. Pan and A. W. Xu, *J. Mater. Chem. B*, 2022, **10**, 1453–1462.
- 98 T.-H. Le, Y. Kim and H. Yoon, *Polymers*, 2017, **9**, 150.
- 99 H. Gong, L. Cheng, J. Xiang, H. Xu, L. Feng, X. Shi and Z. Liu, *Adv. Funct. Mater.*, 2013, **23**, 6059–6067.
- 100 C. M. MacNeill, E. M. Wailes and N. H. Levi-Polyachenko, *J. Nanosci. Nanotechnol.*, 2013, **13**, 3784–3791.
- 101 Y. Yang, X. Zhang, C. Yu, X. Hao, J. Jie, M. Zhou and X. Zhang, *Adv. Healthcare Mater.*, 2014, **3**, 906–915.
- 102 H. Yan, L. Zhao, W. Shang, Z. Liu, W. Xie, C. Qiang, Z. Xiong, R. Zhang, B. Li, X. Sun and F. Kang, *Nano Res.*, 2017, **10**, 704–717.
- 103 H. Yan, W. Shang, X. Sun, L. Zhao, J. Wang, Z. Xiong, J. Yuan, R. Zhang, Q. Huang, K. Wang, B. Li, J. Tian, F. Kang and S. S. Feng, *Adv. Funct. Mater.*, 2018, **28**, 1705710.
- 104 L. Resina, F. F. F. Garrudo, C. Alemán, T. Esteves and F. C. Ferreira, *Biomater. Adv.*, 2024, **160**, 213830.
- 105 L. Resina, T. Esteves, S. Pérez-Rafael, J. I. H. García, F. C. Ferreira, T. Tzanov, S. Bonardd, D. D. Díaz, M. M. Pérez-Madrigal and C. Alemán, *Biomater. Adv.*, 2024, **162**, 213925.
- 106 A. Chicheł, J. Skowronek, M. Kubaszewska and M. Kanikowski, *Rep. Pract. Oncol. Radiother.*, 2007, **12**, 267–275.
- 107 H. H. Kampinga, *Int. J. Hyperthermia*, 2006, **22**, 191–196.
- 108 P. Kaur, M. L. Aliru, A. S. Chadha, A. Asea and S. Krishnan, *Int. J. Hyperthermia*, 2016, **32**, 76–88.
- 109 S. Wang, C. Zhang, F. Fang, Y. Fan, J. Yang and J. Zhang, *J. Mater. Chem. B*, 2023, **11**, 8315–8326.
- 110 J. B. Vines, D. J. Lim and H. Park, *Polymers*, 2018, **10**.
- 111 C. Yu, L. Xu, Y. Zhang, P. S. Timashev, Y. Huang and X. J. Liang, *ACS Appl. Polym. Mater.*, 2020, **2**, 4289–4305.
- 112 K. Yang, H. Xu, L. Cheng, C. Sun, J. Wang and Z. Liu, *Adv. Mater.*, 2012, **24**, 5586–5592.
- 113 M. Chen, X. Fang, S. Tang and N. Zheng, *Chem. Commun.*, 2012, **48**, 8934–8936.
- 114 S. Lan, W. Xie, J. Wang, J. Hu, W. Tang, W. Yang, X. Yu and H. Liu, *J. Nanopart. Res.*, 2018, **20**, 300.
- 115 J. Sun, S. Zhu, W. Xu and G. Jiang, *Front. Bioeng. Biotechnol.*, 2022, **10**, 1049437.
- 116 H. Liu, W. Li, Y. Cao, Y. Guo and Y. Kang, *J. Nanopart. Res.*, 2018, **20**, 57.
- 117 T. H. Tran, H. T. Nguyen, T. T. Phuong Tran, S. K. Ku, J.-H. Jeong, H.-G. Choi, C. S. Yong and J. O. Kim, *Nanomedicine*, 2017, **12**, 1511–1523.
- 118 Y. Ma, J. Zhou, Z. Miao, H. Qian and Z. Zha, *ACS Appl. Bio Mater.*, 2019, **2**, 848–855.
- 119 T. E. Kim, H. J. Jang, S. W. Park, J. Wei, S. Cho, W. I. Park, B. R. Lee, C. D. Yang and Y. K. Jung, *ACS Appl. Bio Mater.*, 2021, **4**, 3453–3461.
- 120 R. M. Hathout, A. A. Metwally, S. H. El-Ahmady, E. S. Metwally, N. A. Ghonim, S. A. Bayoumy, T. Erfan, R. Ashraf, M. Fadel, A. I. El-Kholy and J. G. Hardy, *J. Drug Delivery Sci. Technol.*, 2018, **47**, 176–180.
- 121 Z. Zhu and M. Su, *Nanomaterials*, 2017, **7**, 160.
- 122 M. Suneetha, H. Kim and S. S. Han, *Pharmaceutics*, 2023, **15**, 1281.
- 123 Y. Chen, M. Su, L. Jia and Z. Zhang, *Nanomedicine*, 2022, **17**, 1115–1130.
- 124 W. Zhong, K. H. Wong, F. Xu, N. Zhao and M. Chen, *Acta Biomater.*, 2022, **145**, 135–145.
- 125 Y. Li, C. Jiang, D. Zhang, Y. Wang, X. Ren, K. Ai, X. Chen and L. Lu, *Acta Biomater.*, 2017, **47**, 124–134.
- 126 J. Xu, W. Xu, Z. Wang and Y. Jiang, *J. Biomed. Mater. Res., Part A*, 2023, **111**, 158–169.
- 127 Q. Shu, J. Liu, Q. Chang, C. Liu, H. Wang, Y. Xie and X. Deng, *ACS Biomater. Sci. Eng.*, 2021, **7**, 5497–5505.
- 128 T. Du, T. Yang, L. Xu, X. Li, G. Yang and S. Zhou, *Adv. NanoBiomed Res.*, 2022, **2**, 2200076.
- 129 Y. Liu, K. Ai and L. Lu, *Chem. Rev.*, 2014, **114**, 5057–5115.
- 130 Y. Fu, L. Yang, J. Zhang, J. Hu, G. Duan, X. Liu, Y. Li and Z. Gu, *Mater. Horiz.*, 2021, **8**, 1618–1633.
- 131 J. Zhou, Z. Lu, X. Zhu, X. Wang, Y. Liao, Z. Ma and F. Li, *Biomaterials*, 2013, **34**, 9584–9592.
- 132 Y. Hong, W. Cho, J. Kim, S. Hwang, E. Lee, D. Heo, M. Ku, J.-S. Suh, J. Yang and J. H. Kim, *Nanotechnology*, 2016, **27**, 185104.
- 133 E. I. Yslas, L. E. Ibarra, M. A. Molina, C. Rivarola, C. A. Barbero, M. L. Bertuzzi and V. A. Rivarola, *J. Nanopart. Res.*, 2015, **17**, 389.
- 134 Y. Zhang, F. Fang, Y. Chen, M. Li, L. Li, W. Li and J. Zhang, *Chin. J. Chem. Eng.*, 2021, **38**, 221–228.
- 135 W. Wang, R. Narain and H. Zeng, in *Polymer Science and Nanotechnology*, Elsevier, 2020, pp. 203–244.
- 136 N. K. Preman, R. R. Barki, A. Vijayan, S. G. Sanjeeva and R. P. Johnson, *Eur. J. Pharm. Biopharm.*, 2020, **157**, 121–153.
- 137 H. Idrees, S. Z. J. Zaidi, A. Sabir, R. U. Khan, X. Zhang and S. Hassan, *Nanomaterials*, 2020, **10**, 1970.
- 138 S. Liu, Y. Fu, G. Li, L. Li, H. K. Law, X. Chen and F. Yan, *Adv. Mater.*, 2017, **29**, 1701733.
- 139 D. Esrafilzadeh, J. M. Razal, S. E. Moulton, E. M. Stewart and G. G. Wallace, *J. Controlled Release*, 2013, **169**, 313–320.
- 140 K. Krukiewicz, M. Cichy, P. Ruszkowski, R. Turczyn, T. Jarosz, J. K. Zak, M. Lapkowski and B. Bednarczyk-Cwynar, *Mater. Sci. Eng., C*, 2017, **73**, 611–615.
- 141 A. Giordano and G. Tommonaro, *Nutrients*, 2019, **11**, 2376.
- 142 S. R. Saptarshi, A. Duschl and A. L. Lopata, *J. Nano-biotechnol.*, 2013, **11**, 26.
- 143 X. Hu, S. Liu, G. Zhou, Y. Huang, Z. Xie and X. Jing, *J. Controlled Release*, 2014, **185**, 12–21.
- 144 B. Zhang, H. Wang, S. Shen, X. She, W. Shi, J. Chen, Q. Zhang, Y. Hu, Z. Pang and X. Jiang, *Biomaterials*, 2016, **79**, 46–55.



- 145 C. Tommasino, L. Gambardella, M. Buoncervello, R. J. Griffin, B. T. Golding, M. Alberton, D. Macchia, M. Spada, B. Cerbelli, G. d'Amati, W. Malorni, L. Gabriele and A. M. Giammarioli, *J. Exp. Clin. Cancer Res.*, 2016, **35**, 137.
- 146 C. V. Prasad, V. L. Nayak, S. Ramakrishna and U. V. Mallavadhani, *Chem. Biol. Drug Des.*, 2018, **91**, 220–233.
- 147 D. Killock, *Nat. Rev. Clin. Oncol.*, 2015, **12**, 190.
- 148 F. Tian, C. Wang, M. Tang, J. Li, X. Cheng, S. Zhang, D. Ji, Y. Huang and H. Li, *Oncotarget*, 2016, **7**, 51934–51942.
- 149 N. Hosseini-Nassab, D. Samanta, Y. Abdolazimi, J. P. Annes and R. N. Zare, *Nanoscale*, 2017, **9**, 143–149.
- 150 A. C. Anselmo and S. Mitragotri, *Bioeng. Transl. Med.*, 2019, **4**, e10143.
- 151 M. A. Dobrovolskaia, P. Aggarwal, J. B. Hall and S. E. McNeil, *Mol. Pharmaceutics*, 2008, **5**, 487–495.
- 152 D. Fan, Y. Cao, M. Cao, Y. Wang, Y. Cao and T. Gong, *Signal Transduction Targeted Ther.*, 2023, **8**, 293.
- 153 A. Sontheimer-Phelps, B. A. Hassell and D. E. Ingber, *Nat. Rev. Cancer*, 2019, **19**, 65–81.
- 154 L. Neufeld, E. Yeini, S. Pozzi and R. Satchi-Fainaro, *Nat. Rev. Cancer*, 2022, **22**, 679–692.
- 155 R. Paliwal, R. J. Babu and S. Palakurthi, *AAPS PharmSci-Tech*, 2014, **15**, 1527–1534.
- 156 O. Adir, M. Poley, G. Chen, S. Froim, N. Krinsky, J. Shklover, J. Shainsky-Roitman, T. Lammers and A. Schroeder, *Adv. Mater.*, 2020, **32**, 1901989.
- 157 D. Schletz, M. Breidung and A. Fery, *J. Phys. Chem. C*, 2023, **127**, 1117–1125.
- 158 N. David, W. Sun and C. W. Coley, *Nat. Comput. Sci.*, 2023, **3**, 362–364.

