


Cite this: *Nanoscale*, 2025, 17, 2567

Photogenerated charge carrier dynamics on Pt-loaded SrTiO₃ nanoparticles studied *via* transient-absorption spectroscopy†

Fumihiko Ichihara,^{a,b} Hong Pang,^{a,b} Tetsuya Kako,^a Detlef W. Bahnemann^c and Jinhua Ye^{*a,b}

Loading cocatalysts on semiconductor-based photocatalysts to create active reaction sites is a preferable method to enhance photocatalytic activity and a widely adopted strategy to achieve effective photocatalytic applications. Although theoretical calculations suggest that the broad density of states of noble metal cocatalysts, such as Pt, act as a recombination center, this has never been experimentally demonstrated. Herein, we employed pico–nano and nano–micro second transient absorption spectroscopy to investigate the often overlooked photogenerated holes, instead of the widely studied electrons on Pt- and Ni-loaded SrTiO₃ to evaluate the effects of cocatalysts as a recombination center. It is demonstrated that Pt serves as the recombination center with no sacrificial agent; recombination can be suppressed by a hole scavenger, while recombination is not significant on Ni with localized density of states. It is also found that photo-generated holes in SrTiO₃ tend to migrate to Pt within 400 ps, and photo-generated holes generated in the bulk gradually migrate to Pt cocatalysts in a micro-second regime.

Received 12th November 2024,

Accepted 8th January 2025

DOI: 10.1039/d4nr04725g

rsc.li/nanoscale

1. Introduction

Photocatalysis has garnered significant attention as a green technology since it can utilize sunlight to convert ubiquitous molecules, such as water, carbon dioxide and nitrogen, into chemical energy.^{1–13} Despite extensive efforts, its efficiency still remains far from industrial demands, and its practical use has not been achieved yet. One approach to improving photocatalytic efficiency is loading “cocatalysts” on photocatalysts. Certain cocatalysts are known as rectifiers for efficient photocatalytic hydrogen evolution reactions (HERs) and oxygen evolution reactions (OERs). For example, Pt,^{14,15} Ni, NiO^{16–19} and CrO_x/Rh²⁰ are established cocatalysts for the HER, and IrO₂,^{21,22} RuO₂,^{21,23} CoPi (cobalt phosphate)^{24–27} and CoO_x^{15,28,29} are frequently used as cocatalysts for the OER. There are two primary purposes of loading cocatalysts: (i) to reduce the overpotential required for the respective redox process and (ii) to inhibit the recombination of photogene-

rated charge carriers by securing and storing electrons or holes. While the former purpose has been verified using electrochemical measurements, there is limited experimental evidence to confirm the latter purpose with regard to carrier collection behavior.

In the field of theoretical calculations, cocatalyst loading is predicted to act as a recombination center.³⁰ When Pt is loaded on TiO₂, the broad density of states of Pt overlaps with the conduction band minimum and valence band maximum of TiO₂. Thus, it is expected that both photo-generated electrons and holes are captured by Pt cocatalysts. Consequently, the recombination is promoted. Furthermore, even though Pt is an excellent cocatalyst for hydrogen generation, the Pt cocatalyst is not suitable for complete water splitting owing to its backward reaction, in which the generated hydrogen and oxygen recombine and revert to water.³¹ Conversely, in the case of transition metals such as Ni and Co, localized 3d orbitals do not serve as a bridge between the conduction band and valence band.^{32,33} It is therefore expected to result in a relatively low recombination when such transition metals are loaded as cocatalysts. As described above, the cocatalyst plays a crucial but complicated role in the photocatalyst design, and it is essential to obtain experimental insights into how cocatalyst loading influences charge carrier dynamics.

Transient absorption spectroscopy is a very useful technique for measuring and evaluating such recombination pro-

^aResearch Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan.

E-mail: PANG.Hong@nims.go.jp, Jinhua.YE@nims.go.jp

^bGraduate School of Chemical Sciences and Engineering, Hokkaido University, Sapporo Hokkaido 060-0814, Japan

^cInstitute for Technical Chemistry, Leibniz University Hannover, Hannover 30167, Germany

†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4nr04725g>



cesses in semiconductors and reactions proceeding on the surface of a photocatalyst.^{34–39} This method allows for the observation of non-emission carrier dynamics in the semiconductor, following photoexcitation. It has already been applied to investigate the carrier dynamics of Pt-TiO₂,³⁴ NiO-NaTaO₃,⁴⁰ Pt-LaTiO₂N,¹⁵ CoPi-Fe₂O₃,^{41,42} Pt, Au-CdS,^{43,44} Ni-CdS,⁴⁵ and MoS₂-CdS.⁴⁶ However, in many cases, the measurements are focused on the carriers that are anticipated to migrate, and the role of the cocatalyst as a recombination center has not been sufficiently discussed. For instance, in the case of Pt-TiO₂ where electrons are highly expected to migrate to Pt cocatalysts, the migration behavior of the photogenerated holes is often overlooked.

In this study, we used transient absorption spectroscopy to observe the interaction between photo-excited holes and the broad density of states of Pt on SrTiO₃, and compared these results with the situation using the Ni cocatalyst. By examining the carrier dynamics loading of Pt and Ni, the relationship between the cocatalyst type and recombination dynamics is discussed.

2. Experimental section

2.1 Photocatalyst preparation

SrTiO₃ nanoparticles were synthesized through a polymerizable complex method.⁴⁷ Specifically, Ti(OC₄H₉)₄ (99.9%, Sigma-Aldrich) was dissolved in ethylene glycol, and the mixture was stirred under N₂ atmosphere for 30 min. Afterwards, Sr(NO₃)₂ (99.9%, Sigma-Aldrich) and citric monohydrate (99.5%, Carl Roth) were added, and the stirring was continued until the solution became completely transparent. The reaction mixture was subsequently stirred for an additional 15 minutes to ensure full dissolution of the reagents, and then heated at 120 °C for 5 hours to promote polymerization. During heating, the solvent evaporated and the suspension transformed into a transparent brownish resin. This resin was further heated to 350 °C with a slow ramping temperature rate (1 °C min⁻¹) and kept for 3 hours. The resulting cinders were ground to obtain fine nanoparticles, and further calcined at 750 °C for 6 hours.

2.2 Photo-deposition of the cocatalyst and photocatalytic reaction

Pt and Ni photo-deposition was carried out in 300 ml of 10 vol% methanol (MeOH) aqueous solution, and the evaluation of the photocatalytic hydrogen evolution was continued after the deposition. 50 mg SrTiO₃ powder was placed in a Pyrex glass reactor, and subjected to ultrasonic treatment for 30 minutes. Then, H₂PtCl₆·6H₂O or Ni(NO₃)₂ aqueous solution was added with vigorous stirring for the Pt and Ni photo-deposition, respectively. The photocatalytic activity evaluation was performed with a gas-closed circulation system, as shown in Fig. S1.† The Pyrex glass reactor and solution were degassed by linking to a gas-closed circulation system connected to a rotary pump. The solution was irradiated for 3 hours with the full arc

of a 300 W Xe lamp for the photo-deposition and photocatalytic reaction. The produced H₂ was analyzed by gas chromatography (GC) (GC-8A, Shimadzu, Japan; carrier gas, Ar) with a thermal conductivity detector (TCD), which was connected to the gas-closed circulation system.

2.3 Characterization

The sample was characterized by X-ray diffraction (XRD: D8 Advance; Bruker Corp, Germany) using Cu K α radiation in the 2 θ range of 10–70° with a step width of 0.01°. The diffused reflectance spectra of the sample were recorded on a UV-visible spectrometer (UV-2600; Shimadzu, Japan) with BaSO₄ as the reference. The reflectance spectra were converted to absorption spectra by the Kubelka–Munk function. The photoluminescence (PL) spectra of the sample were recorded on a FP-8550 (JASCO, Japan) with the excitation wavelength of 355 nm. The microstructure observations were performed with transmission electron microscopy (TEM, JEM-ARM200F; JEOL Ltd, Japan) at an acceleration voltage of 60 kV. X-ray photoelectron spectroscopy (XPS) analysis was performed on a EnviroESCA (SPECS GmbH, Germany) equipped with Al K α radiation, and the pass energy for all measurements was set to 20 eV. *I*–*V* measurements were performed by potentiostat (SP-300; Bio-Logic SAS, France) with the voltage range of –6 to 6 V.

Charge carrier dynamics were measured by transient absorption spectroscopy. The details of the set-up of the nano-micro^{48,49} and pico-nanosecond transient absorption are described in Fig. S2 and S3,† respectively. For the transient absorption experiments, the powder photocatalysts were packed in a quartz cuvette, which allowed for the introduction of reactant gases. Here, O₂ gas and MeOH vapor were applied as electron and hole scavengers, respectively.^{34,35}

3. Results and discussion

3.1 The characterization of Pt, Ni-loaded SrTiO₃

Fig. 1(a and b) shows the XRD patterns of the synthesized SrTiO₃ and Pt and Ni-loaded SrTiO₃. The synthesized SrTiO₃ shows a perovskite structure with the lattice constant of *a* = 3.9233 Å, which is relatively consistent with the reported value of *a* = 3.911 Å.⁵⁰ In addition, no other diffraction patterns were observed after the Pt and Ni cocatalyst is loaded, indicating that the Pt and Ni cocatalyst was loaded as relatively small particles. Fig. 1(c and d) shows the UV-Vis absorption spectra of (c) Pt and (d) Ni-loaded SrTiO₃. SrTiO₃ exhibits light absorption in the UV range, as reported in the previous literature.⁴⁹ Fig. 1(c) shows an increase in absorption in the 400–700 nm range with increasing loading amount of the Pt cocatalyst, which can be attributed to the absorption of Pt nanoparticles, as observed by TEM (Fig. S4†).⁵¹ In Fig. 1(d), the absorption of Ni-loaded SrTiO₃ increased with increasing Ni loading amount, as in the case of Pt. A slight change in the shape of the shoulder of the absorption edge was observed when the Ni loading amount was 1.0 wt%, indicating that a part of



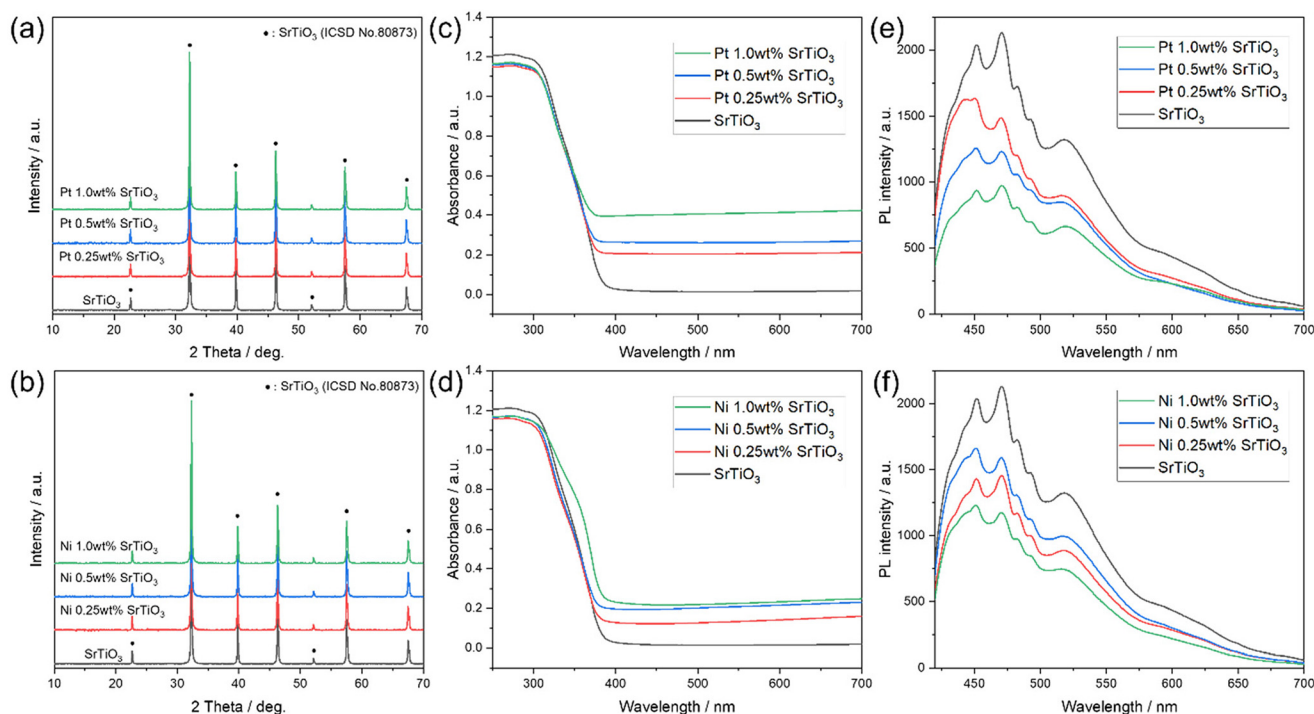


Fig. 1 XRD patterns of (a) Pt and (b) Ni-loaded SrTiO₃. UV-vis absorption spectra of (c) Pt and (d) Ni-loaded SrTiO₃. PL spectra of (e) Pt and (f) Ni-loaded SrTiO₃ with an excitation wavelength of 355 nm.

the Ni cocatalyst was oxidized. Fig. 1(e and f) shows the PL spectra of Pt and Ni-loaded SrTiO₃. The broad photoluminescence signal of SrTiO₃ was derived from a radiative recombination between electrons located in numerous numbers of trapping states between the band gap and holes at the valence band. The PL signal intensity was weakened when the Pt or Ni cocatalysts were loaded. This is probably due to the non-radiative recombination pathway of the photoexcited electrons formed by cocatalyst loading. Fig. S5† shows the XPS spectra of the Pt and Ni 1.0 wt%-loaded SrTiO₃. Fig. S5(a and b)† shows that the carbon species and -OH groups adsorbed on SrTiO₃ were reduced by the loading process of the cocatalyst. This is considered to be due to the removal of the surface adsorbed species by the photocatalytic effect of SrTiO₃ irradiated with light during the loading process. The chemical states of Ti and Sr shown in Fig. S5(c and d)† showed only limited changes due to the loading of the cocatalyst, indicating that the cocatalyst can be loaded without causing side reactions, such as alloying and/or elemental interdiffusion. The chemical states of Pt and Ni shown in Fig. S5(e and f)† indicate that Pt was metallic, while Ni was partially oxidized. This partial oxidation of Ni is considered to correspond to the change in the shape of the absorption edge observed in the UV-Vis spectrum (Fig. 1(d)). Fig. S6† shows the *I*-*V* curves of SrTiO₃ and Pt and Ni-loaded SrTiO₃. The voltage-current response shows no linear response components even after the addition of the Pt or Ni cocatalysts, indicating that the junction between SrTiO₃ and the cocatalyst is a Schottky junction.

3.2 The photocatalytic activity of the Pt, Ni-loaded SrTiO₃

Fig. 2(a) shows the effect of Pt loading on the photocatalytic HER activities of the SrTiO₃ nanoparticles. The results show that the photocatalytic activity was significantly enhanced from 25.5 $\mu\text{mol g}^{-1} \text{h}^{-1}$ to 851.3, 1149.4, 1386.3 $\mu\text{mol g}^{-1} \text{h}^{-1}$ with the increase of the Pt weight percent from 0.0 to 0.25, 0.5, and 1.0 wt%, respectively. This is reasonable as loading noble metals such as Pt is expected to create active sites for HER. However, the photocatalytic activity gets saturated with further increases in the Pt loading. Therefore, the loaded Pt contents affect the electron-hole recombination rate in SrTiO₃ nanoparticles. Fig. 2(b) shows the photocatalytic HER activities with respect to the amount of Ni that is loaded. A similar trend was observed in the case of Ni loading up to 1.0 wt%, although the activity at 1.0 wt% was as low as 205 $\mu\text{mol g}^{-1} \text{h}^{-1}$, approximately one-seventh of that achieved with Pt.

3.3 Transient absorption of photogenerated charge carriers in SrTiO₃

Fig. 3(a) shows the transient absorption spectrum after the irradiation with a 355 nm Nd:YAG laser over SrTiO₃. The energy of the Nd:YAG laser is a suitable excitation wavelength to induce a band-to-band transition of SrTiO₃. A broad absorption band is observed around 765 nm, and a relatively narrow absorption band is observed around 825 nm. To identify the observed carriers, decay measurements were taken at 765 nm with the presence of an electron scavenger (O₂ gas) and a hole scavenger (MeOH vapor) (Fig. 3(b)). As a reference, a decay



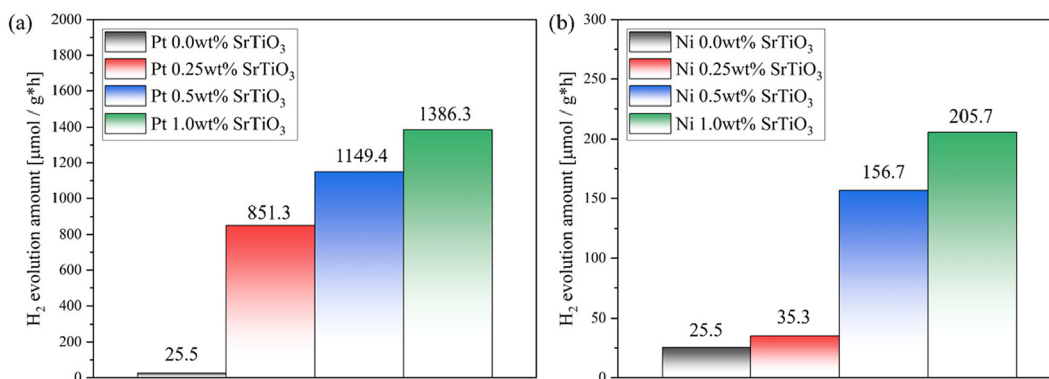


Fig. 2 Effect of the loaded platinum weight percent on the photocatalytic activity of (a) Pt- and (b) Ni-loaded SrTiO₃ nanoparticles for photocatalytic hydrogen evolution.



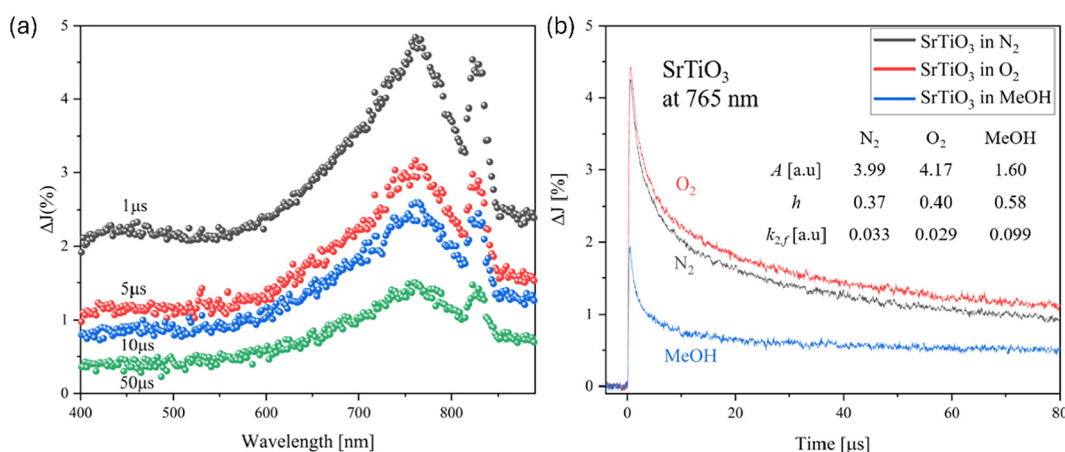


Fig. 3 (a) Transient absorption spectra of SrTiO₃ particles irradiated by a UV (355 nm) pulsed laser under N₂ gas. The pump energy was 1.3 mJ cm⁻², and the repetition rate was 10 Hz. (b) Decay curves of transient absorption of the SrTiO₃ at 765 nm.

measurement was also performed in a N₂ gas atmosphere, where no reactive species are present, representing a simple process of electron-hole recombination. In the measurement under O₂ atmosphere, the decay began to slow down slightly after 1 μs. This is because the electrons that tend to recombine with holes are captured by O₂.⁵²



Where (g) and (a) represent the gas phase and adsorbed phase, respectively. Interestingly, the decay was dramatically accelerated when measuring in MeOH. This is because the holes were collected by MeOH-derived adsorbates:



From the above results, it can be concluded that the photo-excited carriers at 765 nm are transient absorption bands derived from holes. As shown in Fig. S7,[†] the decay of the signal was decelerated in O₂ atmosphere and accelerated in MeOH vapor, similar to the signal seen at 765 nm, indicating a hole-derived transient absorption signal.

3.4 Transient absorption of photogenerated charge carriers over Pt, Ni-loaded SrTiO₃

Fig. 4(a and b) shows the transient absorption spectra of SrTiO₃ loaded with 0.25 wt% Pt and Ni, respectively. Both transient absorption spectra of Pt and Ni-loaded SrTiO₃ show broad absorption peaks at around 765 nm and 825 nm, similar to those observed on the pure SrTiO₃. This suggests that even after cocatalyst loading, the transient absorption signal reflects the transient feature of SrTiO₃. To further investigate the interaction between the cocatalyst loading and the trapping behavior of photogenerated holes in SrTiO₃, the relationship between the amount of cocatalyst loading and the decay constant in the inert N₂ atmosphere was determined (Fig. 5). The transient absorption spectra of SrTiO₃ loaded with 0.5 wt% and 1.0 wt% Pt or Ni can be found in Fig. S8.[†] The linear increase in *k_{2,f}*, which indicates the rate of decay with respect to the amount of cocatalyst, indicates the transfer of holes to the cocatalyst. This phenomenon is also considered to be reasonable since holes can easily move through the Schottky junction between n-type semiconductors SrTiO₃ and Pt or Ni cocatalysts, as shown in the *I-V*



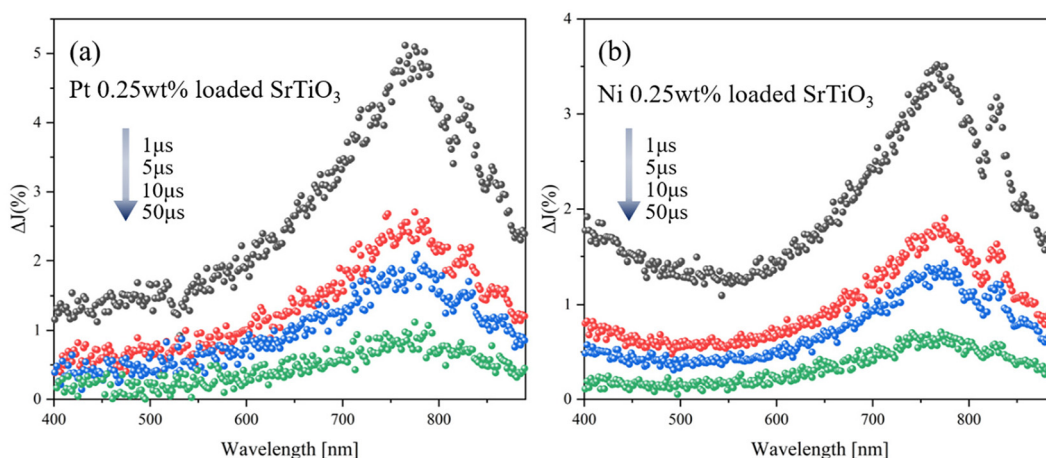


Fig. 4 (a) Transient absorption spectra of Pt 0.25 wt% SrTiO₃ particles and (b) Ni 0.25 wt% SrTiO₃ particles irradiated by a UV (355 nm) pulsed laser under N₂ gas. The pump energy was 1.3 mJ cm⁻², and the repetition rate was 10 Hz.

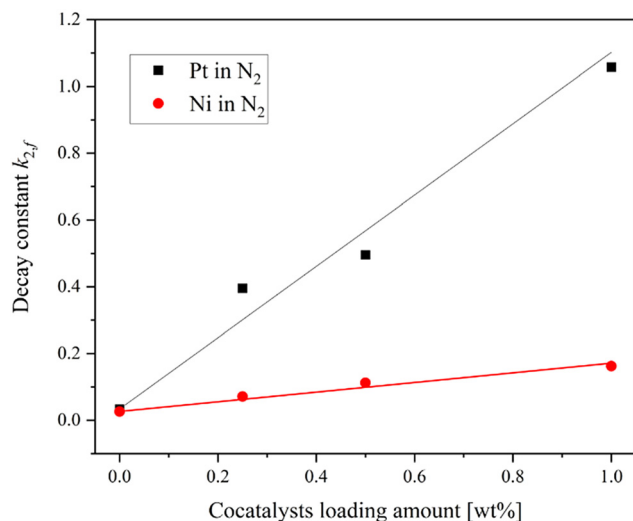


Fig. 5 The relationship between the loading amount of Pt and Ni cocatalysts and the decay constant $k_{2,f}$.

curves (Fig. S6†). The increase in the decay constant $k_{2,f}$ with Pt loading was much more pronounced than that with Ni, suggesting that the broad density of states of Pt act as a recombination center.

Fig. 6(a) exhibits the relationship between the amount of Pt loading and the decay constant of Pt-loaded SrTiO₃ in different atmospheres. As described in Fig. 5, an increasing decay constant in N₂ atmosphere with respect to the increase of the Pt amount has been observed. This increase in decay constant was further promoted in the presence of O₂ gas and suppressed in MeOH vapor (Fig. 6(a)), suggesting that the adsorption of O₂ and MeOH molecules influences the decay dynamics. In contrast, the decay constant of Ni-loaded SrTiO₃, shown in Fig. 6(b), was less affected by the increase in the Ni amount and the various atmospheres.

To further understand the effect of the adsorbed molecules on the Pt cocatalyst, the decay curves of Pt-loaded SrTiO₃ at

765 nm in N₂, O₂ and MeOH atmospheres are compared, as shown in Fig. 7(a). As described in Fig. 6(a), the decay rate accelerates in the O₂ atmosphere and decelerates in MeOH vapor, compared to that of N₂ atmosphere. Unlike SrTiO₃ (Fig. 3(b)), Pt loading causes the transient decay to be slowest in MeOH vapor. In the O₂ atmosphere, the decay rate is slightly accelerated as the decay constant $k_{2,f}$ increases from 0.395 to 0.449, compared with that in N₂ atmospheres. Moreover, Fig. 8 illustrates the decay curves of SrTiO₃ with different loading amounts of Pt at 765 nm in N₂ and MeOH atmospheres. In Fig. 8(a), the Pt loading dramatically decreases the signal intensity and increases the decay constant in a N₂ atmosphere. Meanwhile, in a MeOH atmosphere (Fig. 8(b)), the decrease in signal intensity and increase in decay constant are not as significant as those observed in a N₂ atmosphere. These limited changes in MeOH indicate that MeOH scavenges photogenerated holes in SrTiO₃, thus mitigating the impact of Pt cocatalyst loading on the decay curves. Conversely, as seen in Fig. 7(b) and Fig. S9,† for Ni-loaded SrTiO₃, the decay was decelerated in an O₂ atmosphere and accelerated in a MeOH atmosphere compared with that in a N₂ atmosphere, similar to that of SrTiO₃, confirming that the Ni cocatalyst loading has a small effect on the carrier dynamics of SrTiO₃ and does not act as a recombination center.

From the results discussed above, the dynamics shown in Fig. 9 can be considered as follows: in an O₂ atmosphere, O₂ adsorbed on Pt scavenges the electrons of the Pt cocatalyst to form charged oxygen species and produce holes.^{30,53} These charged oxygen species and the holes generated at the Pt cocatalyst are expected to trap the electron-hole pairs generated in SrTiO₃, accelerating the consumption of charge carriers in the O₂ atmosphere compared to the N₂ atmosphere. In the case of MeOH vapor, MeOH molecules tend to scavenge the photo-generated holes in SrTiO₃. Thus, there is no large effect observed over the carrier dynamics from loading different amounts of Pt cocatalyst. Therefore, the recombination at the



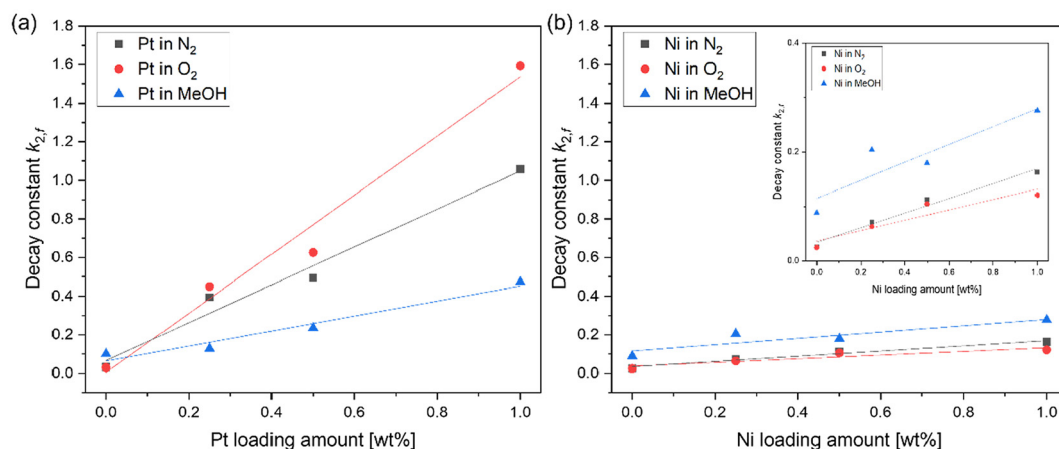


Fig. 6 (a) The relationship between the loading amount of Pt cocatalysts, (b) Ni cocatalyst and decay constant k_{2f} in different atmospheres. The inset figure shows the enlarged vertical axis of (b).

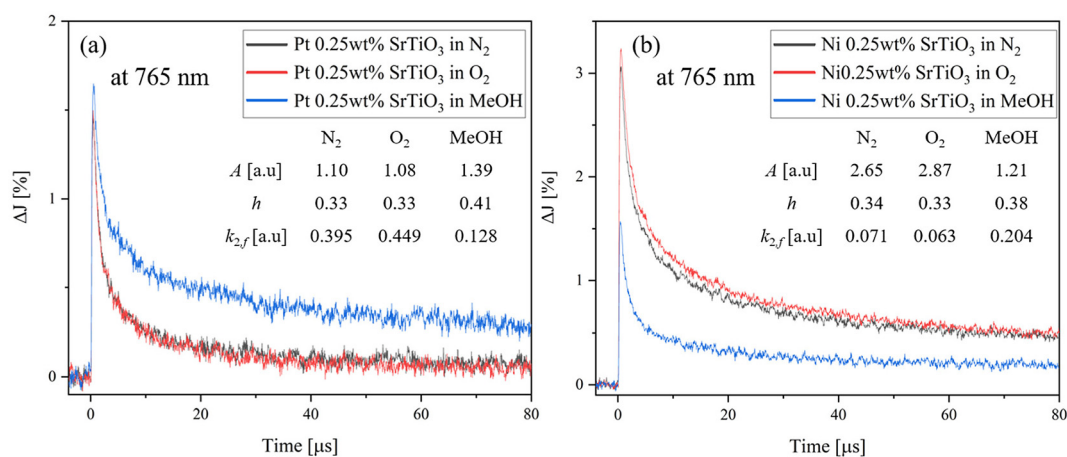


Fig. 7 Decay curves of the transient absorption of (a) Pt 0.25 wt%-loaded $SrTiO_3$ and (b) Ni 0.25 wt%-loaded $SrTiO_3$ in different atmospheres at 765 nm.

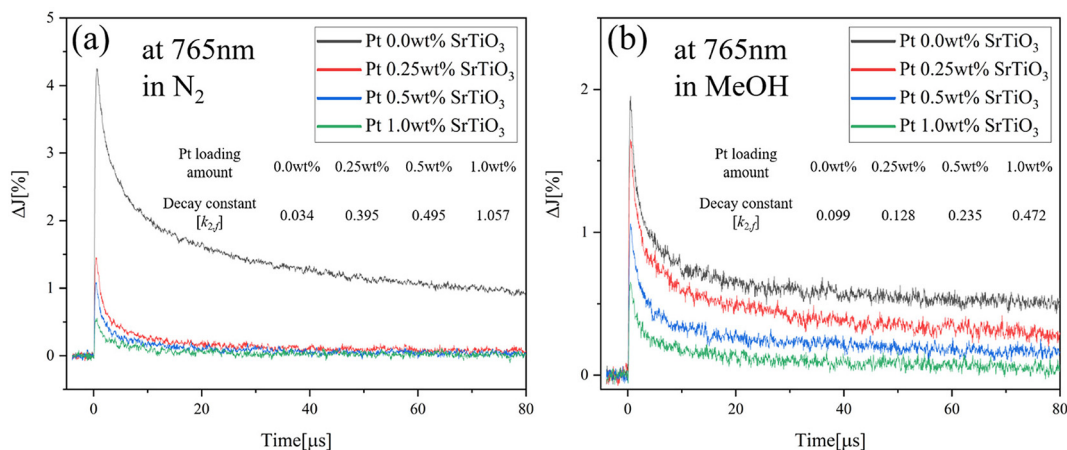


Fig. 8 Decay curves of transient absorption of the Pt-loaded $SrTiO_3$ in (a) N_2 and (b) MeOH atmospheres at 765 nm.



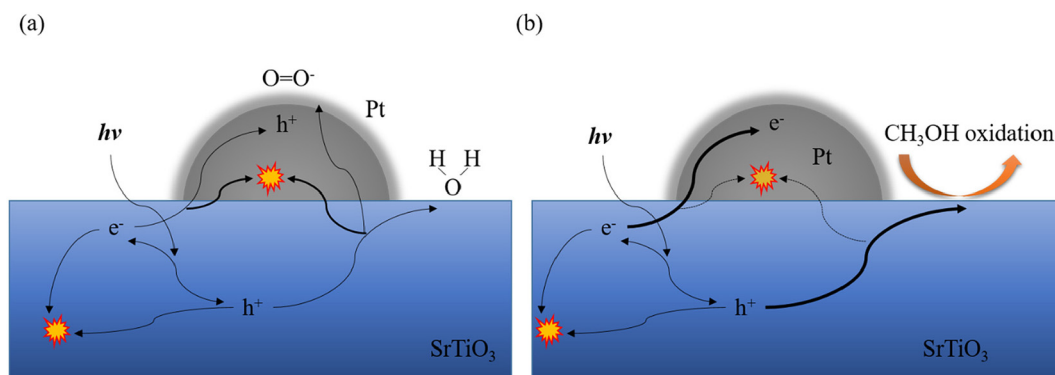


Fig. 9 Schematic representation of the photoexcited electron and hole path over Pt-loaded SrTiO₃ in the presence of (a) O₂ gas and (b) MeOH vapor.

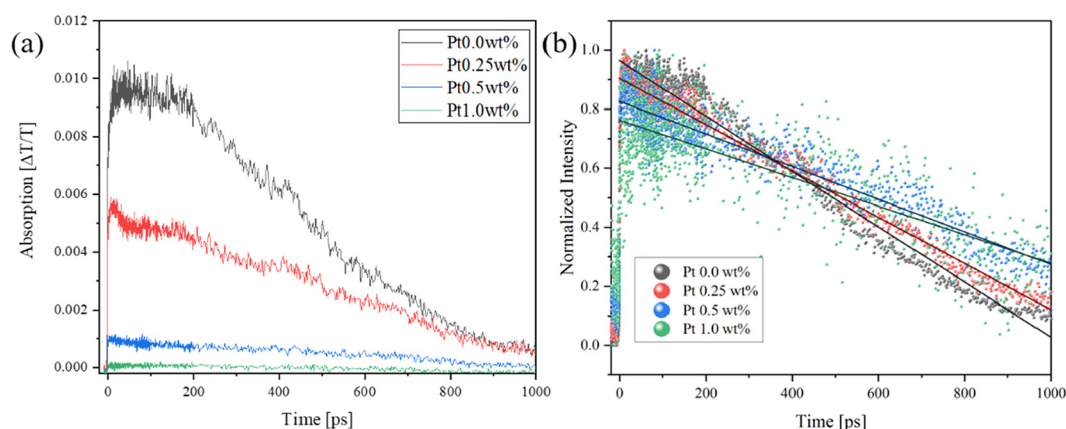


Fig. 10 (a) Pico-second transient absorption spectra and (b) normalized spectra of Pt-loaded SrTiO₃ nanoparticles irradiated by UV (355 nm) pulsed laser under ambient conditions at 765 nm.

Pt cocatalyst has been suppressed in the presence of hole sacrificial reagents.

3.5 Hole behavior observed by femtosecond transient absorption measurement

The photocatalytic reaction takes place in three steps, *i.e.*, carrier generation, charge transfer, and surface reaction.⁵² In order to investigate the time scale on which the photo-generated holes transfer, we measured the transient absorption spectrum at 765 nm on the pico-second scale, as shown in Fig. 10(a). When Pt was loaded on SrTiO₃, the sample itself absorbed light at 765 nm, and the signal intensity decreased with an increase in the Pt loading amount. After normalizing the spectra (Fig. 10(b)), it was observed that the photo-excitation showed a faster decay than pure SrTiO₃ as the Pt loading increased up to about 400 ps. This is similar to the accelerated decay of LaTiO₂N, which has the same perovskite structure as SrTiO₃, in the range of 2–350 ps due to Pt loading.¹⁵ However, the lifetime was extended after 400 ps. This phenomenon indicates that photoexcited holes near the surface were effectively transferred to the Pt cocatalysts within

400 ps. Beyond this time frame, hole trapping behavior from the bulk did not occur within the pico-nano second time range of the transient absorption measurement. As described above, the holes were likely drawn and recombined in Pt cocatalysts in the micro-second range.

4. Conclusion

SrTiO₃ samples loaded with Pt and Ni cocatalysts by photodeposition were evaluated and compared using nano-micro and pico-micro second transient absorption spectroscopy. Focusing on the transient absorption signal derived from holes, rather than the normally studied electron signals, it was found that the decay constant, representing the speed of carrier decay, increased linearly with the loading amount of cocatalysts. When loading with the Pt cocatalyst, this increase in the decay constant was more significant than that with Ni cocatalyst loading, indicating that the broad density of state of Pt may act as a recombination center, as suggested by theoretical calculation. In MeOH vapor, this increasing recombina-



This journal is © The Royal Society of Chemistry 2025

- 41 S. R. Pendlebury, M. Barroso, A. J. Cowan, K. Sivula, J. Tang, M. Grätzel, D. Klug and J. R. Durrant, Dynamics of photogenerated holes in nanocrystalline α -Fe₂O₃ electrodes for water oxidation probed by transient absorption spectroscopy, *Chem. Commun.*, 2011, **47**(2), 716–718, DOI: [10.1039/C0CC03627G](https://doi.org/10.1039/C0CC03627G).
- 42 M. Barroso, A. J. Cowan, S. R. Pendlebury, M. Grätzel, D. R. Klug and J. R. Durrant, The Role of Cobalt Phosphate in Enhancing the Photocatalytic Activity of α -Fe₂O₃ toward Water Oxidation, *J. Am. Chem. Soc.*, 2011, **133**(38), 14868–14871, DOI: [10.1021/ja205325v](https://doi.org/10.1021/ja205325v).
- 43 K. Wu, Z. Chen, H. Lv, H. Zhu, C. L. Hill and T. Lian, Hole Removal Rate Limits Photodriven H₂ Generation Efficiency in CdS-Pt and CdSe/CdS-Pt Semiconductor Nanorod–Metal Tip Heterostructures, *J. Am. Chem. Soc.*, 2014, **136**(21), 7708–7716, DOI: [10.1021/ja5023893](https://doi.org/10.1021/ja5023893).
- 44 K. Wu, W. E. Rodríguez-Córdoba, Y. Yang and T. Lian, Plasmon-Induced Hot Electron Transfer from the Au Tip to CdS Rod in CdS-Au Nanoheterostructures, *Nano Lett.*, 2013, **13**(11), 5255–5263, DOI: [10.1021/nl402730m](https://doi.org/10.1021/nl402730m).
- 45 Y. Nakibli, Y. Mazal, Y. Dubi, M. Wächter and L. Amirav, Size Matters: Cocatalyst Size Effect on Charge Transfer and Photocatalytic Activity, *Nano Lett.*, 2018, **18**(1), 357–364, DOI: [10.1021/acs.nanolett.7b04210](https://doi.org/10.1021/acs.nanolett.7b04210).
- 46 Z. Yan, L. Du and D. L. Phillips, Multilayer, core–shell MoS₂/CdS nanorods with very high photocatalytic activity for hydrogen production under visible-light excitation and investigation of the photocatalytic mechanism by femtosecond transient absorption spectroscopy, *RSC Adv.*, 2017, **7**(88), 55993–55999, DOI: [10.1039/C7RA12118K](https://doi.org/10.1039/C7RA12118K).
- 47 S. Tonda, S. Kumar, O. Anjaneyulu and V. Shanker, Synthesis of Cr and La-codoped SrTiO₃ nanoparticles for enhanced photocatalytic performance under sunlight irradiation, *Phys. Chem. Chem. Phys.*, 2014, **16**(43), 23819–23828, DOI: [10.1039/C4CP02963A](https://doi.org/10.1039/C4CP02963A).
- 48 J. Schneider, K. Nikitin, M. Wark, D. W. Bahnemann and R. Marschall, Improved charge carrier separation in barium tantalate composites investigated by laser flash photolysis, *Phys. Chem. Chem. Phys.*, 2016, **18**(16), 10719–10726, DOI: [10.1039/C5CP07115A](https://doi.org/10.1039/C5CP07115A).
- 49 F. Ichihara, F. Sieland, H. Pang, D. Philo, A.-T. Duong, K. Chang, T. Kako, D. W. Bahnemann and J. Ye, Photogenerated Charge Carriers Dynamics on La- and/or Cr-Doped SrTiO₃ Nanoparticles Studied by Transient Absorption Spectroscopy, *J. Phys. Chem. C*, 2020, **124**(2), 1292–1302, DOI: [10.1021/acs.jpcc.9b09324](https://doi.org/10.1021/acs.jpcc.9b09324).
- 50 S. Keshri, L. Joshi and S. S. Rajput, Studies on La_{0.67}Ca_{0.33}MnO₃–SrTiO₃ composites using two-phase model, *J. Alloys Compd.*, 2011, **509**(19), 5796–5803, DOI: [10.1016/j.jallcom.2011.02.122](https://doi.org/10.1016/j.jallcom.2011.02.122).
- 51 K. K. R. Datta, M. Eswaramoorthy and C. N. R. Rao, Water-solubilized aminoclay–metal nanoparticle composites and their novel properties, *J. Mater. Chem.*, 2007, **17**(7), 613–615, DOI: [10.1039/B617198B](https://doi.org/10.1039/B617198B).
- 52 J. Schneider, M. Matsuoka, M. Takeuchi, J. Zhang, Y. Horiuchi, M. Anpo and D. W. Bahnemann, Understanding TiO₂ Photocatalysis: Mechanisms and Materials, *Chem. Rev.*, 2014, **114**(19), 9919–9986, DOI: [10.1021/cr5001892](https://doi.org/10.1021/cr5001892).
- 53 P. A. Pepin, J. D. Lee, C. B. Murray and J. M. Vohs, Thermal and Photocatalytic Reactions of Methanol and Acetaldehyde on Pt-Modified Brookite TiO₂ Nanorods, *ACS Catal.*, 2018, **8**(12), 11834–11846, DOI: [10.1021/acscatal.8b03081](https://doi.org/10.1021/acscatal.8b03081).

