


Showcasing work from the laboratory of Eiji Yashima,  
Department of Molecular Design and Engineering,  
Nagoya University, Japan.

Helix–helix inversion of an optically-inactive  $\pi$ -conjugated  
foldamer triggered by concentration changes of a single  
enantiomeric guest leading to a change in the helical stability

An optically inactive poly(phenyleneethynylene)-based foldamer  
undergoes a unique helicity induction and subsequent inversion  
of the helicity upon complexation with an increasing amount of  
a single enantiomeric diamine, accompanied by a remarkable  
change in the stability of the helices.

As featured in:

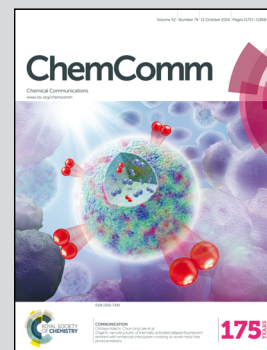

See Naoki Ousaka,  
Eiji Yashima *et al.*,  
*Chem. Commun.*, 2016, 52, 11752.



Cite this: *Chem. Commun.*, 2016, 52, 11752

Received 13th July 2016,  
Accepted 18th August 2016

DOI: 10.1039/c6cc05753e

www.rsc.org/chemcomm

# Helix–helix inversion of an optically-inactive $\pi$ -conjugated foldamer triggered by concentration changes of a single enantiomeric guest leading to a change in the helical stability†

Lijia Liu,<sup>ab</sup> Naoki Ousaka,<sup>\*a</sup> Miki Horie,<sup>a</sup> Fumihiko Mamiya<sup>a</sup> and Eiji Yashima<sup>\*a</sup>


**A preferred-handed helicity induced in an optically-inactive poly(phenyleneethynylene)-based foldamer bearing carboxylic acid pendants upon complexation with a single enantiomeric diamine was subsequently inverted into the opposite helix upon further addition of the diamine, accompanied by a remarkable change in the stability of the helices.**

Stimuli-triggered switching or inversion of macromolecular and supramolecular helicity including a foldamer in a controllable manner has become a fascinating research area of polymer and supramolecular chemistry in the last two decades, because of potential application to chiral materials for asymmetric catalysis, chiral sensing and chiral separation.<sup>1</sup> Among them, the inversion of the helicity in optically active helical systems has been successfully achieved *via* various external stimuli, such as temperature,<sup>2</sup> solvent,<sup>1g,2g,3</sup> photo-irradiation<sup>4</sup> and chiral<sup>2g,5</sup> or achiral additives.<sup>6</sup>

Previously, we reported a thermo- or solvent-driven helicity inversion of a preferred-handed helical polymer induced by only a single enantiomer through noncovalent interactions in a dynamically racemic helical poly(phenylacetylene) bearing phosphonate pendants.<sup>7</sup> However, there are only a few examples of such a noncovalent approach to produce diastereomeric right- and left-handed helices from such racemic helices upon complexation with a non-racemic guest.<sup>7,8</sup> We now report a unique helicity induction and subsequent inversion of the helicity in an optically inactive poly(phenyleneethynylene) (PPE)-based foldamer<sup>1c,9</sup> composed of alternating achiral *o*-diethynylphthalic acid and *p*-phenyleneethynylene (PE) units (poly-1) upon

complexation with the increasing amount of a single enantiomeric diamine (A1), thus producing pseudo-diastereomeric right- and left-handed helices (Fig. 1). Interestingly, the stability of the diastereomeric helices was significantly dependent on the helical senses induced by different amounts of the chiral diamine. An analogous optically-active PPE-based foldamer bearing chiral substituents (poly-2) was also prepared for comparison.

The optically-inactive and active (3–7) monomers and polymers (poly-1 and poly-2) (Fig. 1a) were prepared according to Scheme S1 (ESI†). The achiral PPE-based foldamer with methoxymethyl (MOM) protecting groups (poly-1-MOM) was synthesized by the

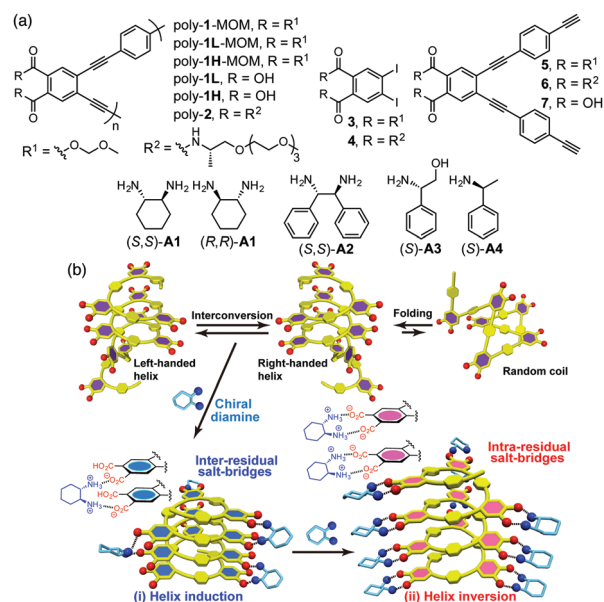

**Fig. 1** (a) Chemical structures of poly(phenyleneethynylene) derivatives, monomers, and chiral amines. L, H, and MOM represent low and higher molecular weight parts of the fractionated poly-1-MOM or poly-1, and methoxymethyl, respectively. (b) Schematic representation of a preferred-handed helicity induction in an optically inactive poly-1 with a small amount of (S,S)-A1 (i) and subsequent inversion of the induced helicity upon further addition of (S,S)-A1 (ii). The plausible interaction modes are also depicted.

<sup>a</sup> Department of Molecular Design and Engineering, Graduate School of Engineering, Nagoya University, Chikusa-ku, Nagoya 464-8603, Japan.  
E-mail: ousaka@apchem.nagoya-u.ac.jp, yashima@apchem.nagoya-u.ac.jp;  
Fax: +81 52-789-3185

<sup>b</sup> Polymer Materials Research Center, Key Laboratory of Superlight Materials and Surface Technology, Ministry of Education, College of Materials Science and Chemical Engineering, Harbin Engineering University, Harbin, 150001, China

† Electronic supplementary information (ESI) available: Experimental details and additional spectroscopic data. See DOI: 10.1039/c6cc05753e



copolymerization of *o*-diiodo benzene **3** with the diethynyl monomer **5** using the palladium/copper-catalyzed Sonogashira cross-coupling reaction, producing a poly(*o*-PE-*alt*-*p*-PE)-based foldamer poly-**1**-MOM in a high yield (84%). In order to investigate the chain-length effect of the polymer on the chiroptical properties, the resulting poly-**1**-MOM was fractionated into a higher molecular weight fraction (poly-**1H**-MOM,  $M_n = 6.7 \times 10^3$ ) and a low molecular weight fraction (poly-**1L**-MOM,  $M_n = 4.4 \times 10^3$ ) using size-exclusion chromatography (Table S1, ESI<sup>†</sup>), followed by deprotection of the MOM groups, affording amphiphilic poly-**1H** and poly-**1L** consisting of the hydrophobic PE backbone and hydrophilic carboxyl side chains (Fig. 1a). In a similar way, an amphiphilic, chiral-amide-appended PPE-based foldamer (poly-**2**,  $M_n = 9.9 \times 10^3$ ) was also prepared from the corresponding monomers **4** and **6** (Fig. 1a and Table S1, ESI<sup>†</sup>).

Because of the amphiphilic nature of poly-**1**, it is important to choose a suitable solvent system to induce the solvophobic-driven helical folding in the PE backbone.<sup>1c,9</sup> Therefore, an H<sub>2</sub>O/THF mixture (6.5/3.5, v/v) was chosen as the solvent, because poly-**1H** and poly-**1L** are hardly soluble in pure H<sub>2</sub>O, which is a poor solvent for the PE backbone. The folding properties of poly-**1L** in the absence and presence of a series of enantiopure mono-(**A3**, **A4**) and diamines (**A1**, **A2**) were first investigated *via* a combination of circular dichroism (CD), UV-vis and fluorescence measurements, which is known to be a powerful method to obtain valuable information on the helical folding for analogous foldamers composed of *o*-PE,<sup>9c,d</sup> *o*-PE-*alt*-*p*-PE,<sup>9f,g</sup> and *m*-PE<sup>1c,9a,b,e</sup> backbones.

In the presence of a small amount of (*S,S*)- and (*R,R*)-*trans*-1,2-cyclohexanediamine **A1** (0.19 equiv. to the *o*-PE monomer unit), the optically inactive poly-**1L** exhibited perfect mirror-image induced CD (ICD) spectra in the H<sub>2</sub>O/THF mixture (ii and iv, Fig. 2a),<sup>10</sup> whereas no ICD was observed for both poly-**1L** in DMSO and monomer **7** in H<sub>2</sub>O/THF (6.5/3.5, v/v) even with an excess of (*S,S*)-**A1** (Fig. S1, ESI<sup>†</sup>). The CD spectral pattern induced in poly-**1L** with (*R,R*)-**A1** is very similar to that of the optically-active poly-**2** (Fig. S2, ESI<sup>†</sup>).<sup>11</sup> In addition, we previously reported that an analogous oligomer composed of the same optically-active *o*-PE units folds into a right-handed helical conformation stabilized by intramolecular hydrogen bonds between the side-chain amide groups.<sup>12</sup> These results suggest that poly-**1L** complexed with a small amount of (*R,R*)-**A1** most likely takes the same right-handed helical conformation.

The ICD intensity gradually increased with an increase in the amount of (*S,S*)-**A1**, along with both a significant reduction in the fluorescence intensity at around 450 nm and an apparent hypochromic effect in the absorption spectra, until an amount of **A1** of 0.19 equiv. was reached (Fig. 2b and Fig. S3a, c, ESI<sup>†</sup>). Such a fluorescence quenching is typical for the helical folding of the PE-based foldamers due to a tight  $\pi$ - $\pi$  stacking interaction between the non-adjacent PE units,<sup>1c,9</sup> as supported by the close contact between the *o*-PE units (average distance of *ca.* 3.6 Å) in the energy-minimized structure of the left-handed helical poly-**1** (9mer) (Fig. 3); the calculated CD spectrum matches well with the experimental one of poly-**1L** induced in the presence of a small amount of (*S,S*)-**A1** (Fig. S4, ESI<sup>†</sup>). Therefore,

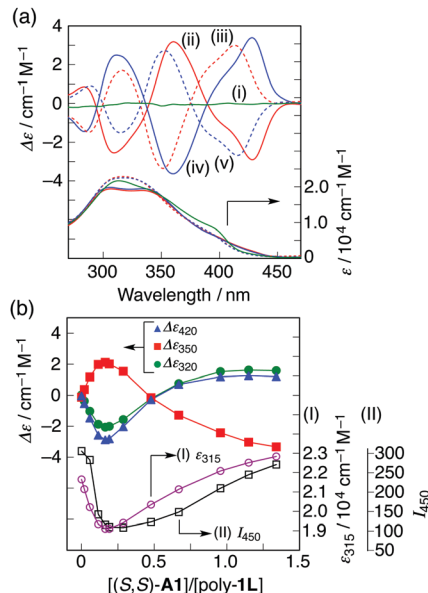


Fig. 2 (a) CD and absorption spectra of poly-**1L** in the absence (i) and presence of (*S,S*)-**A1** (ii, iii) and (*R,R*)-**A1** (iv, v) in H<sub>2</sub>O/THF (6.5/3.5, v/v) at 25 °C: [poly-**1L**] =  $6.8 \times 10^{-5}$  M per monomer unit and [**A1**]/[poly-**1L**] = 0.19 (ii, iv) and 1.3 (iii, v). (b) Plots of CD intensity (left axis) at 420, 350 and 320 nm, molar absorptivity (right axis I) at 315 nm and fluorescence intensity (right axis II) at 450 nm of poly-**1L** versus the molar ratio of (*S,S*)-**A1** to poly-**1L** in H<sub>2</sub>O/THF (6.5/3.5, v/v) at 25 °C.

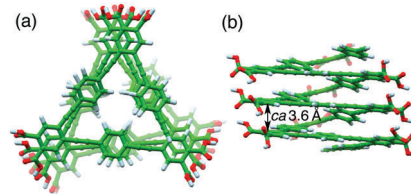


Fig. 3 Top (a) and side (b) views of the energy-minimized left-handed helical structure of poly-**1** (9mer) obtained via the semiempirical molecular orbital calculations. The average distance between two *o*-linked benzene rings at *i* and *i* + 3th positions is also shown.

the preferred-handed helical structure of poly-**1L** with the tight  $\pi$ - $\pi$  stacking can be induced by complexation with the enantiopure **A1**, despite the resulting electrostatic repulsion between the negatively charged, spatially closed carboxylate groups at the side chains. This repulsive interaction might be compensated by the noncovalent intramolecular cross-linking of the two peripheral carboxylate groups along the helical poly-**1L** through the salt-bridge formation with two positively charged ammonium groups of **A1** as a noncovalent cross-linker (Fig. 1b, (i)), thus leading to the close packing between the non-adjacent *o*-PE units, accompanied by the fluorescence quenching as already described. In sharp contrast, the fluorescence intensities at 415 and 450 nm of poly-**1L** were drastically enhanced by the increasing amount of monoamines (*S*)-**A3** and (*S*)-**A4** (Fig. S5 and S6, ESI<sup>†</sup>).<sup>9f,g</sup> This is likely due to a weak single electrostatic interaction between the ammonium and carboxylate groups of poly-**1L** that enhances the electrostatic repulsion between the carboxylate groups as a result



of the dissociation of the ammonium–carboxylate ion pairs, thus leading to a random coil structure. Therefore, poly-1L showed no ICD in the presence of the chiral monoamines.

Interestingly, the further addition of (*S,S*)-A1 to the poly-1L complexed with 0.19 equiv. of (*S,S*)-A1 initially resulted in a significant decrease in the ICD intensity, followed by inversion of the Cotton effect signs concomitant with an apparent hyperchromic effect in the absorption spectra at higher concentrations of (*S,S*)-A1 (Fig. 2 and Fig. S3b, ESI†). This inversion of the Cotton effect signs was accompanied by a large increase in the fluorescence intensity at around 450 nm (Fig. S3d, ESI†), indicating that the poly-1L complexed with 1.3 equiv. of (*S,S*)-A1 possessed an opposite handed helical structure with a slightly loose stacking of the *o*-PE units as compared to the poly-1L with 0.19 equiv. of (*S,S*)-A1. The difference in the helical stacking structures of the *o*-PE units of poly-1L resulting from the different salt bridge formations (inter-residual and intra-residual, Fig. 1b) was further revealed by their thermal stability. As anticipated, the poly-1L complexed with 1.3 equiv. of (*S,S*)-A1 through intra-residual salt-bridges was highly sensitive to temperature and its ICD almost disappeared at 55 °C (Fig. 4b), whereas the ICD signal of the poly-1L with 0.19 equiv. of (*S,S*)-A1 was retained at 55 °C due to the noncovalent intramolecular cross-linking through the salt-bridge formation between the two peripheral carboxylate groups of the *o*-PE units and ammonium groups of A1 (Fig. 4a).

When (*S,S*)-A2 was used instead of (*S,S*)-A1, a similar preferred-handed helicity induction of poly-1L was also observed, as evidenced by an ICD signal (Fig. S7a, ESI†). However, the complex did not exhibit inversion of the Cotton effects by the further addition of (*S,S*)-A2, although the absorption and fluorescence spectra changed similar to those observed for (*S,S*)-A1 (Fig. 2b and Fig. S7a–c, ESI†). The reason for this difference in the helix-inversion phenomena depending on the concentrations of (*S,S*)-A1 and (*S,S*)-A2 is not clear at present, but is considered to be due to the difference in their structural rigidity between A1 and A2. The linear diamine A2 is more flexible than the cyclic diamine A1, which may allow A2 to adjust its conformation to form inter-residual salt-bridges with the two spatially closed peripheral carboxylate groups of poly-1L independent of the concentration of A2 (Fig. 1b, (i)).<sup>13</sup> In contrast, such an adjustable conformational change hardly occurred for the rigid cyclic diamine A1, resulting in a change to the intra-residual

salt bridge formation at higher A1 concentrations (Fig. 1b, (ii)), thus leading to the helix-inversion.

Similar preferred-handed helicity induction and subsequent inversion of the helicity depending on the concentration of (*S,S*)- and (*R,R*)-A1 was also observed for the higher molecular weight poly-1H, and the complexes showed mirror image ICDs whose CD spectral patterns were similar to those of poly-1L (Fig. 5a and Fig. S8, ESI†), and (*S,S*)-A2 did not induce the helicity inversion of poly-1H (Fig. S9, ESI†). The maximum ICD intensities at 350 nm of poly-1H before and after the helicity inversion triggered by a change in the concentration of (*S,S*)-A1 were approximately 2.5 times greater than those of poly-1L (Fig. 2a and 5a). This is because the increasing main-chain length enhances the helical stability of the foldamers<sup>9b,e,g</sup> probably resulting from an inter-chain interaction at the side chains, which is also supported by the fact that the fluorescence spectrum of poly-1H alone was similar to that of the more closely packed helical poly-1L stabilized by 0.19 equiv. of (*S,S*)-A1 (Fig. S3c and S8c, ESI†). Moreover, the complex formation of poly-1H with the non-racemic A1 resulted in a positive nonlinear ICD response with respect to the enantiomeric excess (ee) of A1 (majority rule),<sup>14</sup> indicating an amplification of the helix-sense excess that takes place during the folding process (Fig. 5b and Fig. S10a, ESI†), whereas the lower molecular weight poly-1L did not exhibit such a positive non-linearity (Fig. 5b and Fig. S11, ESI†).<sup>15</sup> Interestingly, the ICD intensity of poly-1H complexed with 0.5 equiv. of the enantiopure and non-racemic A1 was significantly enhanced with time, resulting in a higher degree of the nonlinear ICD response (Fig. 5b, Fig. S10b and S12, ESI†). The observed higher amplification of the helical handedness excess of poly-1H may be ascribed to the aggregation of the induced helical poly-1H,<sup>16</sup> whose size was roughly estimated to be ca. 20–100 nm by filtration experiments using membrane filters with different pore sizes (Fig. S13, ESI†).<sup>17</sup> In sharp contrast, a mixture of poly-1L with 0.19 equiv. of (*S,S*)-A1 did not show such time-dependent ICD changes (Fig. S14, ESI†).

In summary, we have demonstrated a preferred-handed helicity induction and subsequent inversion of the helicity triggered

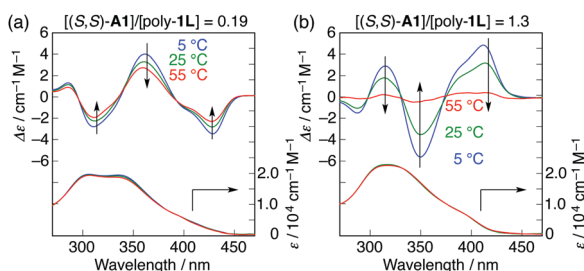


Fig. 4 Temperature-dependent CD and absorption spectral changes of poly-1L in the presence of different amounts of (*S,S*)-A1 ([A1]/[poly-1L] = 0.19 (a) and 1.3 (b)) in H<sub>2</sub>O/THF (6.5/3.5, v/v): [poly-1L] = 6.8 × 10<sup>-5</sup> M per monomer unit.

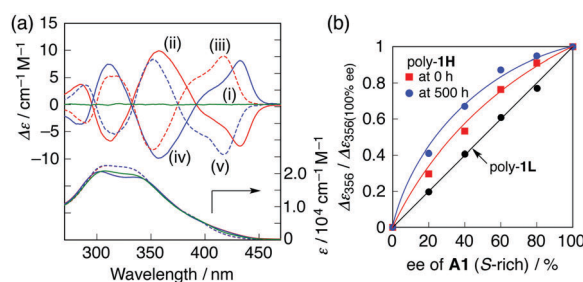


Fig. 5 (a) CD and absorption spectra of poly-1H in the absence (i) and presence of (*S,S*)-A1 (ii, iii) and (*R,R*)-A1 (iv, v) measured immediately after the addition of A1 in H<sub>2</sub>O/THF (6.5/3.5 v/v) at 25 °C: [poly-1H] = 8.2 × 10<sup>-5</sup> M per monomer unit and [A1]/[poly-1H] = 0.2 (ii, iv) and 1.3 (iii, v). (b) Plots of normalized CD intensity at 356 nm of poly-1H versus % ee value of A1 in H<sub>2</sub>O/THF (6.5/3.5, v/v) at 25 °C measured at 0 (red square) and 500 h (blue circle) after the addition of A1: [poly-1H] = 8.2 × 10<sup>-5</sup> M per monomer unit and [(*S,S*)-A1]/[poly-1H] = 0.5. Plots of normalized CD intensity at 356 nm of poly-1L versus % ee value of A1 are also shown (black circle): [poly-1L] = 6.8 × 10<sup>-5</sup> M per monomer unit, [A1]/[poly-1L] = 0.19.



by the increasing amount of a single enantiomeric diamine in an optically inactive poly(*o*-PE-*alt*-*p*-PE)-based foldamer bearing carboxylic acid pendants, accompanied by a significant change in the stability of the helical structures. The detailed spectroscopic studies revealed that the stability difference between the pseudo-diastereomeric right- and left-handed helices is ascribed to the difference in the salt-bridge formations between the foldamer and the diamine that are determined by the concentration of the diamine. In addition, the longer foldamer showed an intriguing amplification of the helix-sense excess (the majority rule effect), which was further enhanced with time through supramolecular aggregation. The present results may provide a novel design strategy for the development of supramolecular asymmetric catalysts<sup>18,19</sup> and chiral materials for separating enantiomers<sup>20</sup> based on the helicity-switchable foldamers.

This work was supported in part by JSPS KAKENHI (Grant-in-Aid for Scientific Research (S), no. 25220804 (E. Y.) and Grant Number JP16H01016 in Precisely Designed Catalysts with Customized Scaffolding (N. O.)). M. H. expresses her thanks for a JSPS Research Fellowship for Young Scientists (no. 10192).

## Notes and references

- For recent reviews: (a) D. J. Hill, M. J. Mio, R. B. Prince, T. S. Hughes and J. S. Moore, *Chem. Rev.*, 2001, **101**, 3893; (b) T. Nakano and Y. Okamoto, *Chem. Rev.*, 2001, **101**, 4013; (c) J. S. Moore and C. R. Ray, *Adv. Polym. Sci.*, 2005, **177**, 91; (d) *Foldamers: Structure, Properties, and Applications*, ed. S. Hecht and I. Huc, Wiley-VCH, Weinheim, Germany, 2007; (e) T. F. A. De Greef, M. M. J. Smulders, M. Wolfs, A. P. H. J. Schenning, R. P. Sijbesma and E. W. Meijer, *Chem. Rev.*, 2009, **109**, 5687; (f) E. Yashima, K. Maeda, H. Iida, Y. Furusho and K. Nagai, *Chem. Rev.*, 2009, **109**, 6102; (g) M. Sugimoto, T. Yamamoto, Y. Nagata, T. Yamada and Y. Akai, *Pure Appl. Chem.*, 2012, **84**, 1759; (h) T. Nakano, *Chem. Rec.*, 2014, **14**, 369; (i) J. Shen and Y. Okamoto, *Chem. Rev.*, 2016, **116**, 1094; (j) E. Schwartz, M. Koepf, H. J. Kitto, R. J. M. Nolte and A. E. Rowan, *Polym. Chem.*, 2011, **2**, 33; (k) M. Fujiki, *Symmetry*, 2014, **6**, 677.
- (a) K. Maeda and Y. Okamoto, *Macromolecules*, 1998, **31**, 5164; (b) K. S. Cheon, J. V. Selinger and M. M. Green, *Angew. Chem., Int. Ed.*, 2000, **39**, 1482; (c) M. Fujiki, *J. Am. Chem. Soc.*, 2000, **122**, 3336; (d) K. Morino, K. Maeda and E. Yashima, *Macromolecules*, 2003, **36**, 1480; (e) K. Tang, M. M. Green, K. S. Cheon, J. V. Selinger and B. A. Garetz, *J. Am. Chem. Soc.*, 2003, **125**, 7313; (f) J. Tabei, R. Nomura, F. Sanda and T. Masuda, *Macromolecules*, 2004, **37**, 1175; (g) K. Maeda, H. Mochizuki, M. Watanabe and E. Yashima, *J. Am. Chem. Soc.*, 2006, **128**, 7639; (h) Z. Huang, S.-K. Kang, M. Banno, T. Yamaguchi, D. Lee, C. Seok, E. Yashima and M. Lee, *Science*, 2012, **337**, 1521; (i) M. Shigeno, Y. Kushida and M. Yamaguchi, *J. Am. Chem. Soc.*, 2014, **136**, 7972.
- (a) K. Maeda, N. Kamiya and E. Yashima, *Chem. – Eur. J.*, 2004, **10**, 4000; (b) T. Yamamoto, T. Yamada, Y. Nagata and M. Sugimoto, *J. Am. Chem. Soc.*, 2010, **132**, 7899; (c) Y. Nagata, T. Nishikawa and M. Sugimoto, *J. Am. Chem. Soc.*, 2014, **136**, 15901.
- (a) S. Mayer, G. Maxein and R. Zentel, *Macromolecules*, 1998, **31**, 8522; (b) N. Koumura, R. W. J. Zijlstra, R. A. van Delden, N. Harada and B. L. Feringa, *Nature*, 1999, **401**, 152; (c) J. Li, G. B. Schuster, K.-S. Cheon, M. M. Green and J. V. Selinger, *J. Am. Chem. Soc.*, 2000, **122**, 2603; (d) D. Pijper and B. L. Feringa, *Angew. Chem., Int. Ed.*, 2007, **46**, 3693; (e) Z. Yu and S. Hecht, *J. Polym. Sci., Part A: Polym. Chem.*, 2015, **53**, 313.
- (a) E. Yashima, Y. Maeda and Y. Okamoto, *J. Am. Chem. Soc.*, 1998, **120**, 8895; (b) Y. Inai, Y. Ishida, K. Tagawa, A. Takasu and T. Hirabayashi, *J. Am. Chem. Soc.*, 2002, **124**, 2466; (c) P. A. Korevaar, S. J. George, A. J. Markvoort, M. M. J. Smulders, P. A. J. Hilbers, A. P. H. J. Schenning, T. F. A. De Greef and E. W. Meijer, *Nature*, 2012, **481**, 492.
- (a) I. Otsuka, R. Sakai, T. Satoh, R. Kakuchi, H. Kaga and T. Kakuchi, *J. Polym. Sci., Part A: Polym. Chem.*, 2005, **43**, 5855; (b) R. M. Meudtner and S. Hecht, *Angew. Chem., Int. Ed.*, 2008, **47**, 4926; (c) H. Miyake, H. Kamon, I. Miyahara, H. Sugimoto and H. Tsukube, *J. Am. Chem. Soc.*, 2008, **130**, 792; (d) S. Akine, S. Hotate and T. Nabeshima, *J. Am. Chem. Soc.*, 2011, **133**, 13868; (e) F. Freire, J. M. Seco, E. Quinoa and R. Riguera, *Angew. Chem., Int. Ed.*, 2011, **50**, 11692; (f) J.-m. Suk, V. R. Naidu, X. Liu, M. S. Lah and K.-S. Jeong, *J. Am. Chem. Soc.*, 2011, **133**, 13938.
- (a) T. Miyagawa, A. Furuko, K. Maeda, H. Katagiri, Y. Furusho and E. Yashima, *J. Am. Chem. Soc.*, 2005, **127**, 5018; (b) K. Maeda, T. Miyagawa, A. Furuko, H. Onouchi and E. Yashima, *Macromolecules*, 2015, **48**, 4281.
- (a) K. Maeda, K. Morino and E. Yashima, *J. Polym. Sci., Part A: Polym. Chem.*, 2003, **41**, 3625; (b) T. Hasegawa, Y. Furusho, H. Katagiri and E. Yashima, *Angew. Chem., Int. Ed.*, 2007, **46**, 5885; (c) M. Waki, H. Abe and M. Inouye, *Angew. Chem., Int. Ed.*, 2007, **46**, 3059; (d) S. Takashima, H. Abe and M. Inouye, *Chem. Commun.*, 2011, **47**, 7455; (e) Q. Gan, Y. Ferrand, N. Chandramouli, B. Kauffmann, C. Aube, D. Dubreuil and I. Huc, *J. Am. Chem. Soc.*, 2012, **134**, 15656.
- (a) J. C. Nelson, J. G. Saven, J. S. Moore and P. G. Wolynes, *Science*, 1997, **277**, 1793; (b) R. B. Prince, J. G. Saven, P. G. Wolynes and J. S. Moore, *J. Am. Chem. Soc.*, 1999, **121**, 3114; (c) T. V. Jones, M. M. Slutsky, R. Laos, T. F. A. de Greef and G. N. Tew, *J. Am. Chem. Soc.*, 2005, **127**, 17235; (d) A. Khan and S. Hecht, *J. Polym. Sci., Part A: Polym. Chem.*, 2006, **44**, 1619; (e) M. T. Stone, J. M. Heemstra and J. S. Moore, *Acc. Chem. Res.*, 2006, **39**, 11; (f) N. Zhu, W. Hu, S. Han, O. Wang and D. Zhao, *Org. Lett.*, 2008, **10**, 4283; (g) N. Zhu, Q. Yan, Z. Luo, Y. Zhai and D. Zhao, *Chem. – Asian J.*, 2012, **7**, 2386.
- An amide-bond formation between poly-1 and **A1** could be ruled out based on a reaction between a model compound **7** (Fig. 1a) and 1.1 equiv. of (*S,S*)-**A1** in D<sub>2</sub>O/THF-*d*<sub>8</sub> (6.5/3.5, v/v) at 25 °C for 12 h.
- The CD spectrum of poly-2 in H<sub>2</sub>O/THF (6.5/3.5, v/v) was hardly changed upon the addition of 1.5 equiv. of (*S,S*)-**A1** and (*R,R*)-**A1**.
- N. Ousaka, T. Yamaguchi and E. Yashima, *Chem. Lett.*, 2014, **43**, 512.
- This hypothesis is supported by the fact that the ICD signal of poly-1L with 1.1 equiv. of (*S,S*)-**A2** was retained at 55 °C (Fig. S7d, ESI†).
- (a) M. M. Green, B. A. Garetz, B. Munoz, H. Chang, S. Hoke and R. G. Cooks, *J. Am. Chem. Soc.*, 1995, **117**, 4181; (b) M. M. Green, J. W. Park, T. Sato, A. Teramoto, S. Lifson, R. L. B. Selinger and J. V. Selinger, *Angew. Chem., Int. Ed.*, 1999, **38**, 3139.
- For an example of molecular-weight-dependent enhancement of the majority rule effect, see: S. K. Jha, K.-S. Cheon, M. M. Green and J. V. Selinger, *J. Am. Chem. Soc.*, 1999, **121**, 1665.
- For examples of aggregation-assisted amplification of helical chirality in the foldamers, see: (a) L. Brunsveld, E. W. Meijer, R. B. Prince and J. S. Moore, *J. Am. Chem. Soc.*, 2001, **123**, 7978; (b) W. Cai, G. T. Wang, P. Du, R. X. Wang, X. K. Jiang and Z.-T. Li, *J. Am. Chem. Soc.*, 2008, **130**, 13450; (c) A. Petitjean, L. A. Cuccia, M. Schmutz and J. M. Lehn, *J. Org. Chem.*, 2008, **73**, 2481; (d) Y. Wang, F. Li, Y. Han, F. Wang and H. Jiang, *Chem. – Eur. J.*, 2009, **15**, 9424; (e) R. Pfukwa, P. H. J. Kouwer, A. E. Rowan and B. Klumperman, *Angew. Chem., Int. Ed.*, 2013, **52**, 11040.
- Interestingly, the ICD signal of poly-1H retained for several hours upon the addition of a large excess (50 equiv.) of achiral ethylenediamine at 5 °C, suggesting a memory of the induced helicity.<sup>18</sup> The further study for this phenomenon is currently underway in our laboratory.
- E. Yashima, K. Maeda and Y. Okamoto, *Nature*, 1999, **399**, 449.
- (a) M. Raynal, P. Ballester, A. Vidal-Ferran and P. W. N. M. van Leeuwen, *Chem. Soc. Rev.*, 2014, **43**, 1660; (b) M. Raynal, P. Ballester, A. Vidal-Ferran and P. W. N. M. van Leeuwen, *Chem. Soc. Rev.*, 2014, **43**, 1734; (c) A. Desmarchelier, X. Caumes, M. Raynal, A. Vidal-Ferran, P. W. N. M. van Leeuwen and L. Bouteiller, *J. Am. Chem. Soc.*, 2016, **138**, 4908.
- K. Shimomura, T. Ikai, S. Kanoh, E. Yashima and K. Maeda, *Nat. Chem.*, 2014, **6**, 429.

