

Materials Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: P. Witte, A. M. van Koten and M. E. Kamminga, *Mater. Adv.*, 2024, DOI: 10.1039/D4MA00539B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Cite this: DOI: 00.0000/xxxxxxxxxx

Tuning the magnetic properties of van der Waals materials by intercalation

Pim Witte,^a Annemijn M. van Koten,^a and Machteld E. Kamminga^aReceived Date
Accepted Date

DOI: 00.0000/xxxxxxxxxx

Recent advances in low-dimensional spintronic devices have resulted in an increased demand for layered van der Waals materials with tunable magnetic properties. To this end, intercalation – the insertion of a guest species in the van der Waals gap between the planes of the host material – proves to be a versatile tool. In this review, we discuss various forms of intercalation that allow for tuning the magnetic properties of van der Waals materials. We focus on alkali metal, transition metal and molecule intercalation, and provide an extensive overview of current research efforts. Furthermore, we highlight typical challenges that materials scientists face in this field, and provide suggestions for future research directions.

1 Introduction

Since the discovery of graphene in 2004,¹ two-dimensional (2D) materials have gathered a lot of interest from the solid-state community.^{2–6} In particular, magnetic van der Waals (vdW) materials were sought after, as these could provide a platform for studying magnetism in the 2D limit, when cleaved to monolayer thickness, and could find applications in spintronic devices.^{6,7} The first example of long-range magnetic order observed in an atomically thin material was introduced in 2016 by Lee *et al.*, who reported stable antiferromagnetic order in a monolayer of FePS₃, observed through Raman measurements.⁸ This was quickly followed in 2017 by the direct observation of spontaneous magnetization in single layer Cr₂Ge₂Te₆⁹ and CrI₃.^{10,11}

In addition to studying magnetism in the 2D limit by means of exfoliation, magnetic vdW materials form the ideal template to develop low-dimensional spintronic applications.¹² In these low-dimensional devices, the interlayer magnetic coupling is of utmost importance to the magnetic properties. However, it remains a challenge to not only understand, but also manipulate this magnetic coupling between neighbouring layers to achieve desired properties for these spin-based electronic applications. In recent years, numerous candidate magnetic vdW materials have been reported, including those based on transition metal halides,^{13–16} transition metal chalcogenides,^{17–19} transition metal phosphorus chalcogenides,^{20–22} and metal oxy- and chalcogenides,^{23–27}. Despite this rapidly growing library of magnetic vdW materials, relatively few layered materials with room temperature magnetic order have been reported, despite this being a requirement for

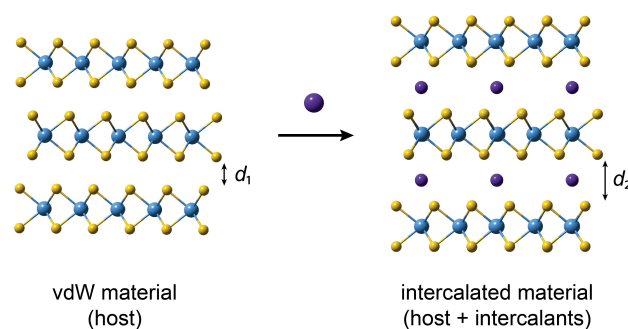


Fig. 1 Schematic illustration of intercalation of vdW materials. The purple spheres represent the intercalants. Upon intercalation, the interlayer distance d_1 increases ($d_2 > d_1$).

several applications.^{28,29}

Therefore, there is a crucial need for tuning the magnetic properties of vdW materials, enabling novel magnetic ordering above room temperature, and expanding the library of magnetic materials. Materials chemists will play a pivotal role in this development, by providing the tools to tune magnetism in vdW materials.

Among strategies to modify the properties of vdW materials, intercalation has become one of the most widely used.^{50,51} In general, intercalation of layered materials is the post-synthetic, reversible process of inserting a foreign ion, atom or molecule in the vdW gap between the layers of the host lattice, as schematically illustrated in Fig. 1.^{52,53} Intercalation is exploited in a wide range of energy storage technologies, spanning from batteries to supercapacitors,^{54–60} and is a powerful tool for modifying the properties of the host material.⁵⁰ The insertion of an intercalant into the interlayer gap, *i.e.* the vdW gap, results in an increased

^a Debye Institute for Nanomaterials Science, Utrecht University, 3508 TA Utrecht, The Netherlands. E-mail: m.e.kamminga@uu.nl



Compound	Method ^a	Order ^b	T_c (K) ^c	Ref.
Fe_2GeTe_3	-	FM	220-230 ^d	[30, 31]
$\text{Li}_x\text{Fe}_2\text{GeTe}_3$	E. Chem.	FM	300	[31]
$(\text{TBA})_x\text{Fe}_2\text{GeTe}_3$	E. Chem.	FM	300	[32]
$\text{Cr}_2\text{Ge}_2\text{Te}_6$	-	FM	67	[9]
$\text{Na}_x\text{Cr}_2\text{Ge}_2\text{Te}_6$	Chem.	FM	240	[33]
$(\text{TBA})_x\text{Cr}_2\text{Ge}_2\text{Te}_6$	E. Chem.	FM	208	[34]
NiPS_3	-	AFM	155	[35]
$(\text{TBA})_{0.25}\text{NiPS}_3$	E. Chem.	FiM	78	[36]
$[\text{Co}(\text{Cp})_2]_{0.25}\text{NiPS}_3$	Ion exch.	FiM	98	[36]
NbS_2	-	-	-	-
$\text{Fe}_{0.25}\text{NbS}_2$	AS	AFM	145	[37]
$\text{Fe}_{0.33}\text{NbS}_2$	AS	AFM	45	[38]
$\text{Cr}_{0.33}\text{NbS}_2$	AS	CHM	127	[16, 39, 40]
TaS_2	-	-	-	-
$\text{Fe}_{0.25}\text{TaS}_2$	AS	FM	160	[41, 42]
$\text{Fe}_{0.33}\text{TaS}_2$	AS	FM	38	[41, 43]
$\text{Cr}_{0.33}\text{TaS}_2$	AS	CHM	142	[44]
CrTe_2	-	FM	310	[45]
Cr_2Te_3 ($\text{Cr}_{1.33}\text{Te}_2$)	AS	FM	180	[46]
Cr_3Te_4 ($\text{Cr}_{1.5}\text{Te}_2$)	AS	FM	320	[46, 47]
CrI_3	-	FM	61	[10, 11, 48]
CrSBr	-	AFM	132	[26, 27, 49]

Table 1 Examples of tunable magnetic properties observed in vdW materials by means of different intercalation methods. ^achemical (Chem.), electrochemical (E. Chem.), ion exchange (Ion Exch.) and as grown from the elements (AS). ^bferromagnetic (FM), antiferromagnetic (AFM), ferromagnetic (FiM) and chiral helimagnetic (CHM). ^c(approximate) magnetic ordering temperature. ^dThis range in T_c depends on the exact amount of Fe in the compound.

interlayer distance, generally reducing the interlayer interaction and making the material “more 2D”. The introduction of a new species also typically results in doping of the host lattice, and new interaction pathways in the material. Consequently, intercalation is a powerful and versatile tool for tuning the properties of materials. For example, intercalation has been used to tune and/or induce superconductivity,^{61–67} charge density waves,^{67–69} and to tune the bandgap,^{70–72} thermoelectric properties,^{73–76} and increasingly, the magnetic properties of vdW materials.

In this review, we focus on tuning the magnetic properties of vdW materials by means of intercalation by highlighting current advances and provide challenges for materials scientists to enhance the field. First, we will discuss common forms of intercalation to tune the magnetic properties of materials, sorted by intercalant type. After that, we will provide challenges for materials scientists and suggestions for future research directions.

2 Types of intercalants

A wide range of intercalants have been used to tune the magnetic properties of vdW materials, ranging from simple monovalent cations to complex intercalants endowing the intercalated host lattice with new properties. In Table 1, we list several examples of such magnetic vdW materials that are tuned by means of intercalation. Note that the table only contains experimental data. Here we will discuss the three most common forms of intercalation currently used to tune magnetic properties in vdW materials: alkali metal intercalation, transition metal intercalation

and molecule intercalation. For each method, we will start by briefly outlining the chemical process of intercalation, followed by its effect on the magnetic properties of the vdW materials.

2.1 Alkali metal intercalation

Alkali metals are typically intercalated using chemical or electrochemical methods. Of the chemical procedures, the most widely used methods are low-temperature intercalation using an alkali metal ammonium solution,^{33,80–83} and high-temperature intercalation using organometallic reagents.^{84–90} Of the organometallic reagents, *n*-butyllithium (*n*-BuLi) is the most commonly used Li⁺ intercalant for its high reduction potential.^{83–86} Intercalation using *n*-BuLi is typically realised by immersing the vdW material in stoichiometric *n*-BuLi hexane under inert atmosphere, and stirring at 100 °C for around 2-3 days. The relatively long reaction time, need for inert atmosphere, and highly flammable nature of *n*-BuLi motivated chemists to look for alternatives to this method. To this end, Li-intercalation has also been achieved using lithium borohydride (LiBH₄),⁸⁷ naphthalenide lithium (Nap-Li),⁹¹ and pyrene lithium (Py-Li).⁸⁸ Note that other alkali metals have been intercalated with various degrees of success using analogous organometallic compounds.^{91,92}

Electrochemical intercalation can be achieved using an electrochemical cell with a metal anode (*e.g.*, Li) and the host vdW material as cathode, separated by an ionically conducting electrolyte.^{31,93–97} The electrochemical intercalation process allows for controlling the intercalation by adjusting the magnitude and polarity of the applied voltage as well as the duration. Moreover, deintercalation can be readily realised by applying the opposite bias, allowing for precise control of the degree of intercalation. The voltage window in which intercalation can occur is determined by the host compound, the electrolyte and the concentration of the intercalant. At more extreme voltages, decomposition can occur. Furthermore, depending on the precise reaction, high degrees of intercalation may only be achieved in an inert atmosphere, requiring a more complex method than chemical intercalation techniques.

2.1.1 Charge doping through alkali metal intercalation

Of the three different types of intercalants discussed in this review, alkali metals are generally the least complex. Alkali cations do not induce magnetic order in nonmagnetic vdW materials, but can be used to tune the magnetic properties of magnetic vdW materials.^{31,33,77–79,86,98–100} Notably, in most cases, intercalation is found to increase the T_c of the material.

The strength of alkali metal intercalation is exemplified by the work of Deng *et al.*, who reported intercalation-dependent ferromagnetism in few-layer Fe_3GeTe_2 ,³¹ one of the most promising materials for spintronic applications due to its metallicity. Note that Fe_3GeTe_2 is prone to Fe deficiency and often written as $\text{Fe}_{3-x}\text{GeTe}_2$ instead, but we will here use Fe_3GeTe_2 to indicate this family of compounds, as often done in literature as well. Deng *et al.* demonstrated that while the T_c of Fe_3GeTe_2 decreases drastically when the number of layers is reduced (see Fig. 2(a)), intercalation with Li gives rise to a sharp increase in T_c , even exceeding that of the bulk sample. This was achieved by intercalat-



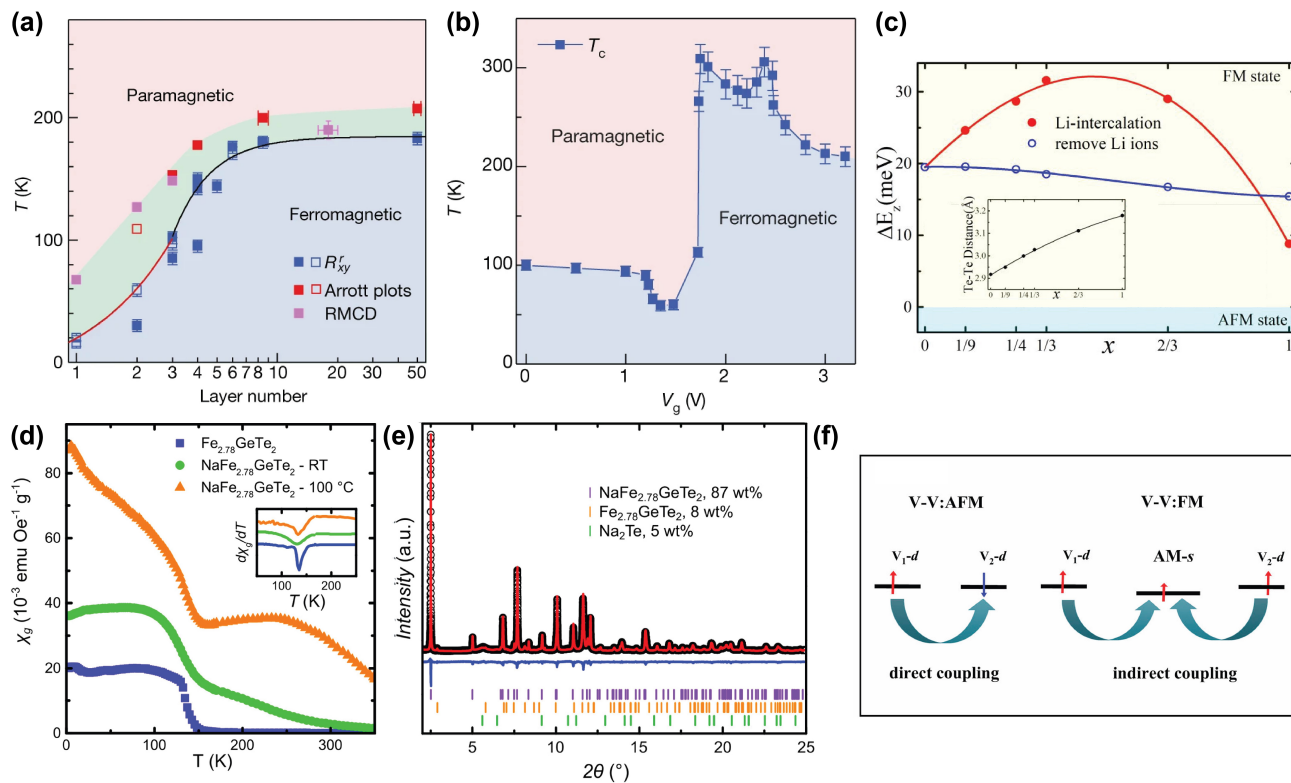


Fig. 2 (a) Magnetic phase diagram of Fe_3GeTe_2 as function of number of layer and temperature. T_C values determined from anomalous Hall measurements (R_{xy}^a), Arrott plots, and refractive magnetic circular dichroism (RMCD), are displayed in blue, red and magenta respectively.³¹ (b) Magnetic phase diagram of trilayer Fe_3GeTe_2 flakes as function of gate voltage (V_g) and temperature. A higher V_g corresponds to a higher degree of Li intercalation. The T_C values were determined from temperature-dependent anomalous Hall measurements, extrapolated to zero.³¹ (c) Calculated interlayer magnetic coupling energy (ΔE_z) in $\text{Li}_x\text{Fe}_3\text{GeTe}_2$ bilayers as function of intercalation level x . The inset displays the calculated interlayer distance between the two interfacial Te sublayers.⁷⁷ (d) Temperature dependence of the specific magnetic susceptibility χ_g of pristine $\text{Fe}_{2.78}\text{GeTe}_2$ (blue squares), Na-intercalated $\text{Fe}_{2.78}\text{GeTe}_2$ (green circles), and Na-intercalated $\text{Fe}_{2.78}\text{GeTe}_2$ annealed at 100°C (orange triangles), measured at 0.01 T . The inset shows the derivative of χ_g , indicating a T_C of $\sim 140\text{ K}$ for all three samples.⁷⁸ (e) Rietveld refinement of $\text{NaFe}_{2.78}\text{GeTe}_2$ ($\lambda = 0.412852\text{ \AA}$), including reflections of unreacted $\text{Fe}_{2.78}\text{GeTe}_2$ (orange) and Na_2Te (green).⁷⁸ (f) Schematic plot of the change in the magnetic exchange mechanism from direct (left) to indirect (right) exchange, in alkali intercalated VS_2 and VSe_2 .⁷⁹ Reproduced from ref. [79]. Reproduced from ref. [31] with permission from Springer Nature, copyright 2018. Reprinted from ref. [77], with the permission of AIP Publishing, copyright 2021. Reprinted with permission from ref. [78]. Copyright 2021 American Chemical Society.

ing trilayer Fe_3GeTe_2 crystal flakes with Li ions through an ionic gate configuration, where a gate voltage V_g was used to intercalate the Li ions into the flakes, akin to charging in Li-ion batteries. As shown in Fig. 2(b), Li intercalation using a small V_g causes a decrease in T_C , but a sharp increase up till room temperature is observed for optimal V_g . Intercalating beyond this point again decreases the T_C .³¹

This remarkable find was supported by first-principle calculations from Huang *et al.*, who suggested that with increasing amount of Li intercalation in Fe_3GeTe_2 , and the associated electron doping of the host lattice, the ferromagnetic interlayer coupling is increased.⁷⁷ However, past a certain doping concentration, this interlayer coupling decreases again (see Fig. 2(c)). This is hypothesised to result from two competing factors: firstly, the intercalated Li ions allow for hopping of charge carriers, resulting in an indirect exchange between the Fe_3GeTe_2 layers that strengthens the interlayer coupling. This becomes particularly apparent at low intercalant concentrations; secondly, at high Li concentrations, the electron transfer from the Li ions to the Fe_3GeTe_2 layers fills the previously unfilled $3d$ orbitals of the Fe

ions, thereby reducing the ferromagnetic coupling.⁷⁷

Although Huang *et al.* were able to model the experimentally observed T_C -increase of Fe_3GeTe_2 upon Li intercalation, reported by Deng *et al.*, the observed initial decrease of T_C is not consistent with this model.^{31,77} Shen *et al.* further investigated this observation by calculating the effect of the electron doping on Fe_3GeTe_2 monolayers using first-principle calculations.¹⁰¹ At low levels of electron doping, they observed a decrease in T_C from 159 K in undoped Fe_3GeTe_2 to 93 K , whereas at higher doping, the T_C increases to 175 K . They hypothesise that the electron doping might tune frustrated intralayer exchange interactions, resulting in the observed evolution of T_C .¹⁰¹ However, as their calculations were performed on monolayer Fe_3GeTe_2 , no interlayer interactions or intercalants were included, making it difficult to directly compare these findings to the results reported by Deng *et al.*

Interestingly, Khan *et al.* recently reported on how electron doping by intercalation of alkali metals can also result in a magnetically-disordered compound.³³ They inhomogeneously intercalated $\text{Cr}_2\text{Ge}_2\text{Te}_6$ with Na ions, resulting in a magnetically frustrated state around 35 K , which is not present in pristine



$\text{Cr}_2\text{Ge}_2\text{Te}_6$. They argue that electron doping through intercalated Na ions alters the ionic states of some of the Cr^{3+} ions into Cr^{2+} , resulting in a double exchange mechanism.³³ The authors also hypothesise that since Cr^{2+} is a Jahn-Teller active ion, its substitution for Cr^{3+} leads to local distortions, increasing local anisotropy and possibly enhancing the spin glass behaviour.

2.1.2 Structural effects of alkali metal intercalation

Besides the possible charge doping described above, alkali metal intercalation also has a strong effect on the structure of the host material and can cause decomposition. For example, Weber *et al.* explored the structural effects of Na intercalation in Fe_3GeTe_2 .⁷⁸ They used Na instead of Li, as it is easier to detect using X-ray diffraction methods. In contrast to Deng *et al.*, who intercalated Fe_3GeTe_2 electrochemically, Weber *et al.* used metallic sodium and benzophenone (Ph_2CO) to intercalate Na into Fe_3GeTe_2 . As a result, they found that the Fe_3FeTe_2 layers become heavily charge-doped and strained via chemical pressure, yet retain their crystal structure. Surprisingly, in great contrast to the Li intercalation discussed above, the intercalation with Na does not affect the ordering temperature, maintaining it at ~ 140 K (see Fig. 2(d)). The main difference with pristine Fe_3GeTe_2 is that the intercalated samples displayed magnetisation above T_C , and even at room temperature. This was attributed to the presence of the defects after Na intercalation. Synchrotron radiation measurements revealed that intercalation had caused some decomposition of the host lattice, resulting in the formation of Na_2Te and amorphous Fe_{2-x}Ge phases (see Fig. 2(e)). As a result, they concluded that the nonzero magnetisation at 300 K could be explained by the presence of ferromagnetic Fe_{2-x}Ge , as well as undetected Fe.⁷⁸ The authors noted that despite the heavy charge doping of $6.95 \times 10^{14} \text{ e}^- \text{ cm}^{-2}$ per Fe_3GeTe_2 layer, this did not result in any significant change in T_C , in sharp contrast to other studies on alkali metal intercalation of Fe_3GeTe_2 . The reason for this could be the difference in intercalation-induced strain in the structure, caused by Li and Na, as intercalation does not only affect the spin density through electron doping, but also the inter- and intralayer bond length and angles, thereby also affecting the magnetic exchange interactions.^{78,93}

Alkali metal intercalation studies typically limit themselves to the use of Li and Na as intercalants, as the larger K and Rb would further increase the interlayer distance, decreasing the interlayer coupling. However, in certain cases, the larger vdW gap created by intercalation of larger alkali metals is beneficial for the magnetic properties of the host lattice, especially in those that contain competing interlayer and intralayer interactions. Intercalation with alkali metals can then tip the balance between these two interactions to favour the intralayer interaction, which can in turn change the type of magnetic order.^{17,79,102,103} An example to illustrate this is VX_2 ($X = \text{S}, \text{Se}$), which is paramagnetic in the bulk, but DFT calculations predicted that it exhibits ferromagnetic intralayer ordering in the monolayer limit.^{102,103} This prediction was experimentally verified for VSe_2 by Bonilla *et al.*¹⁷ In more general terms, these VX_2 ($X = \text{S}, \text{Se}$) systems have direct exchange between the layers that can result in antiferromagnetic coupling, but by intercalation of a large alkali metal

such as K or Rb, the interlayer coupling can be switched from antiferromagnetic to ferromagnetic.⁷⁹ The explanation for this is that when alkali metals are introduced into the vdW gap, their *s*-orbitals can become slightly magnetised by the surrounding magnetic ions through Ruderman–Kittel–Kasuya–Yosida (RKKY) interactions (see Fig. 2(f)). This slight magnetisation then enables the indirect interlayer coupling mediated by the alkali metal ions.

2.2 Transition metal intercalation

Unlike alkali metals, which are exclusively intercalated as cations, transition metals can be intercalated as zerovalent or as cationic species. The intercalation of zerovalent atoms is typically referred to as atom intercalation, to distinguish it from ion intercalation.

A large number of zerovalent transition metals and post-transition metals (Ag, Au, Bi, Co, Cr, Cu, Fe, Ge, Hg, In, Mo, Mn, Ni, Os, Pb, Pd, Pt, Rh, Ru, Sb, Sn, W)^{104–113} have been intercalated into vdW compounds, using a variety of reactions, including disproportionate redox reactions,^{104–107} decomposition of coordination compounds,^{104–106,109} stannous chloride (SnCl_2) reduction,¹⁰⁴ hydrazine reduction,¹⁰⁷ and liquid metal immersion.^{110,111} Electrochemical intercalation of transition metals is not as widely reported as chemical methods, as moving heavy metals electrochemically is much more difficult compared to moving alkali metals.

As charge transfer is often hypothesised to contribute to any change in magnetic properties of transition-metal-intercalated vdW materials, ion intercalation is often used. Note that aside from the chemical post-synthetic methods listed above, and possible solid state reactions between the host material and elemental intercalants,¹¹⁴ transition metal intercalated materials are often synthesised from their constituent elements.^{39,42} While this technically does not qualify as a form of intercalation, the obtained products can be regarded as ‘intercalated products’. Therefore, we purposely chose to include these materials in this review.

Note that despite the large range of possibilities, transition metal intercalation with the aim of tuning the magnetic properties has almost exclusively focused on *3d* metals, especially Fe and Cr, due to their strong magnetic moments.

2.2.1 Tuning magnetism by self-intercalation of magnetic vdW materials

Besides the intercalation of foreign atoms into the vdW gap, the intercalation of native atoms, *i.e.* those that are already present in the vdW material, is particularly interesting. The power of such self-intercalation is well demonstrated by CrTe_2 . By intercalating Cr atoms into the vdW gap between the CrTe_2 layers, different chromium telluride compounds with chemical formula $\text{Cr}_{1+\delta}\text{Te}_2$ ($0 < \delta \leq 1$) are formed (see Fig. 3(a)). This class of materials consists of a broad range of phases,^{45,116–120} and shows a variety of interesting magnetic properties, including skyrmions,¹²¹ biskyrmions,¹²² the magnetocaloric effect,¹²³ and large anomalous Hall effect.^{124,125} As shown in Fig. 3(b), a monotonic positive relationship between T_C and the Cr content has been established.^{45,118,126–129} Alongside this increase in T_C , a reorientation or isotropisation of magnetic anisotropy was reported. In CrTe_2 , all spins are aligned ferromagnetically and out-of-plane



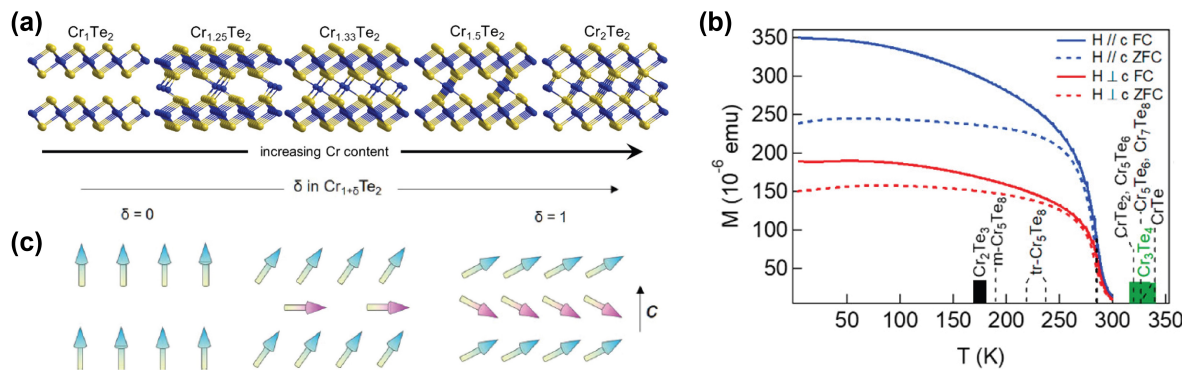


Fig. 3 Self-intercalation of CrTe₂. (a) Crystal structures of CrTe₂ (Cr₁Te₂), Cr_{1.25}Te₂ (Cr₅Te₈), Cr_{1.33}Te₂ (Cr₂Te₃), Cr_{1.5}Te₂ (Cr₃Te₄) and Cr₂Te₂ (CrTe).⁴⁶ (b) Temperature-dependent magnetisation of Cr_{1.5}Te₂, also showing the ordering temperatures of various intercalation levels of CrTe₂.⁴⁶ (c) Schematic drawing of the expected evolution of the ground-state magnetic configuration of Cr_{1+δ}Te₂, with the arrows indicating the local spins.¹¹⁵ Reprinted with permission from ref. [46]. Copyright 2021 American Chemical Society. Reprinted with permission from ref. [115]. Copyright 2020 by the American Physical Society.

with respect to the CrTe₂ layers. When self-intercalated, the magnetic moments of the intercalated Cr atoms tend to align antiferromagnetically with respect to the host layers, inducing non-collinearity (see Fig. 3(c)).^{130,131} In general, the magnetic properties are mainly governed by a competition between antiferromagnetic Cr–Cr direct exchange and ferromagnetic Cr–Te–Cr superexchange.¹³² This self-intercalation introduces more spins into the system, enhancing the superexchange. Note that besides the introduction of additional spins, intercalation also leads to the formation of Cr–Te–Cr bonds, that have a bond angle of $\sim 132^\circ$, which is significantly larger than those of $\sim 90^\circ$ in the host lattice, further enhancing the ferromagnetic coupling.¹³³

Computational studies have also shown that the magnetic properties of CrI₃ and FeCl₂, materials which have garnered a lot of interest from the solid state physics community,^{10,11,136–141} can be tuned using self-intercalation.¹⁴² The self-intercalation of Cr into CrI₃ induces charge transfer from the intercalated Cr ions to the Cr atoms in the host lattice, changing the formal oxidation state of the latter from +3 in pristine CrI₃ to +2.67 in Cr-intercalated CrI₃.¹⁴² This charge transfer induces a double exchange, resulting in an increased ferromagnetic coupling in Cr-intercalated CrI₃ compared to pristine CrI₃.¹⁴²

Similarly, the self-intercalation of Fe into FeCl₂ bilayers has shown to alter the interlayer coupling by charge transfer from the intercalated Fe ions to the host lattice.¹⁴³ Pristine FeCl₂ exhibits strong ferromagnetic intralayer coupling, but antiferromagnetic interlayer coupling, both in its bulk form as in bilayer systems.^{144,145} DFT calculations revealed that the interlayer coupling could be switched from antiferro- to ferromagnetic upon self-intercalation with Fe ions, as the intercalated ions donate charge to the host lattice, resulting in a mixed-valence system. This is responsible for altering the interlayer exchange mechanism from superexchange to double exchange, which favours antiparallel alignment.¹¹² Notably, this even occurs at low levels of Fe intercalation, as the charge transfer from intercalated Fe ions is larger at low concentrations. However, despite the ferromagnetic interlayer coupling not being dependent on the degree of intercalation, the magnetic anisotropy is strongly affected by the

concentration of the intercalated Fe ions. For $\leq 25\%$ Fe intercalation in FeCl₂, the magnetic anisotropy is directed in-plane, whereas for $> 25\%$ Fe intercalation, the anisotropy switches to out-of-plane.¹⁴³

2.2.2 Inducing magnetism by transition metal intercalation of nonmagnetic vdW materials

Aside from tuning inherent magnetic order in vdW materials, intercalation with transition metals is also suitable for *inducing* magnetic order in nonmagnetic host lattices. Good examples of this are the Fe and Cr intercalation of TaS₂ and NbS₂.^{39,42,44,134,146–148} At certain intercalant concentrations, crystallographic superlattices form by a periodic ordering of the intercalants in the octahedral interstitial sites. As shown in Fig. 4(a), superlattices form in Fe_xMS₂ and Cr_xMS₂ with M = Nb or Ta, for $x = 1/4$ and $x = 1/3$.¹³⁴ Due to the distances and bonding motifs between the intercalants in these materials, direct exchange and superexchange are not expected to contribute to the magnetic ordering. The RKKY interactions are considered to be the dominant exchange interaction driving the magnetic ordering.^{149,150} Because Fe_xNbS₂, Fe_xTaS₂, Cr_xNbS₂ and Cr_xTaS₂ are all metallic, it is hypothesised that the localised Fe or Cr 3d electrons couple to the delocalised electrons in the conduction band. However, other studies suggest that the magnetic properties of these compounds are effected by the electronic structure in a manner that cannot be explained by just RKKY theory.^{151,152}

Although Fe_xNbS₂ and Fe_xTaS₂ are isostructural and isoelectronic, they exhibit different magnetic behaviours. For $x < 0.4$, Fe_xTaS₂ orders ferromagnetically whereas Fe_xNbS₂ orders antiferromagnetically, with an easy-axis along the c-axis. The magnetic properties of these intercalated species are very sensitive to small changes in composition, especially around the superlattice stoichiometry $x = 1/3$. At this stoichiometric x , the structures exhibit strong magnetic transitions,^{42,43,153,154} whereas off-stoichiometric Fe_xTaS₂ shows broadened magnetisation switching and large magnetoresistance,^{41,155} and off-stoichiometric Fe_xNbS₂ shows spin glass behaviour and resistive switching.^{146,153} The Fe stoichiometry affects the spacing



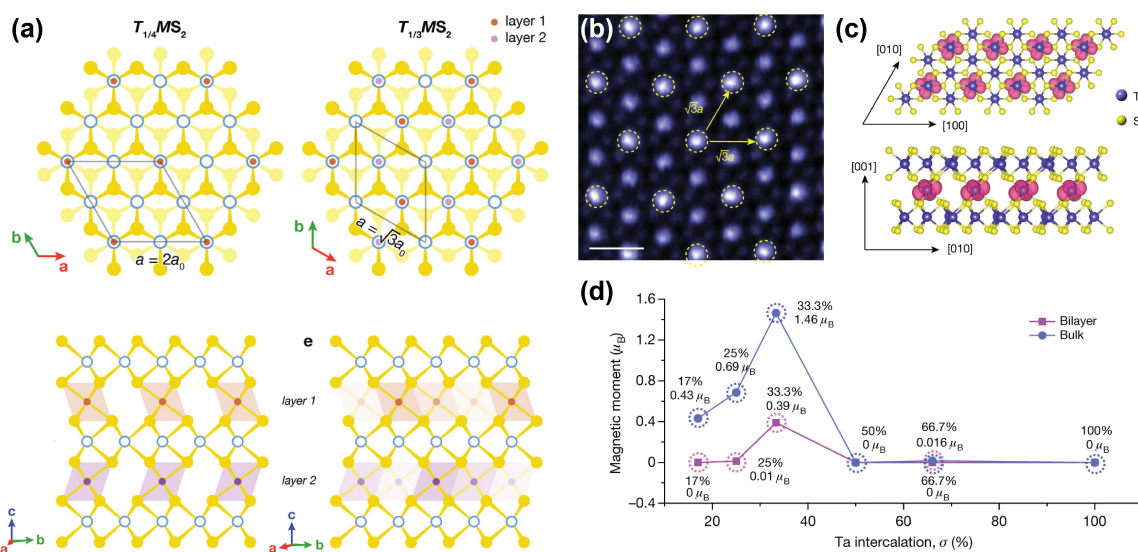


Fig. 4 Inducing magnetic order through transition metal intercalation. (a) Superlattices of Fe_xMS_2 and Cr_xMS_2 with $M = Nb$ or Ta , for $x = 1/4$ and $x = 1/3$.¹³⁴ (b) Atomic-resolution STEM-ADF (Scanning Transmission Electron Microscopy - Angular Dark Field) image of self-intercalated Ta_7S_{12} , showing the superstructure of the intercalated Ta ions. The scale bar corresponds to 0.5 nm.¹³⁵ (c) Top view (top) and side view (bottom) of the spin density isosurface of the intercalated Ta in Ta_7S_{12} .¹³⁵ (d) Calculated magnetic moments as a function of Ta intercalation (σ) in Ta_7S_{12} .¹³⁵ Reprinted with permission from ref. [134]. Copyright 2022 American Chemical Society. Reproduced from ref. [135] with permission from Springer Nature, copyright 2020.

between the magnetic intercalants, thereby altering the magnetic exchange interactions and spatial symmetry of these materials. At high intercalation amounts ($x > 0.4$), antiferromagnetic exchange interactions dominate,¹¹⁴ while at low intercalation amounts ($0.2 \leq x \leq 0.4$) long-range ferromagnetic ordering is observed.^{41,156} The Curie temperature for Fe_xTaS_2 is at its maximum for $x = 1/4$, for which $T_C \approx 160$ K, whereas for $x = 1/3$, $T_C \approx 38$ K, demonstrating the clear difference in magnetic behaviour as a function of Fe content. In contrast to Fe_xTaS_2 , Fe_xNbS_2 exhibits antiferromagnetic order at both $x = 1/4$ and $x = 1/3$, with $T_N \approx 145$ K and $T_N \approx 45$ K, respectively.^{37,38} Most notably, the triangular sublattice formed by the intercalants results in the antiferromagnetic ground state being frustrated. These frustrated exchange interactions play an essential role in the formation of the off-stoichiometric spin glass phases.^{157,158}

Unlike their Fe-intercalated counterparts, Cr_xTaS_2 and Cr_xNbS_2 have their easy-axis in the ab -plane. The lack of inversion symmetry in these systems enables a Dzyaloshinskii–Moriya (DM) interaction that competes with the ferromagnetic ordering, resulting in spin-canting. As a result, both $Cr_{1/3}TaS_2$ and $Cr_{1/3}NbS_2$ exhibit chiral magnetic states.^{39,159–161} The relative strength of this DM interaction increases when exchanging Nb for Ta, because of the increased spin-orbit coupling imparted by Ta compared to Nb. Consequently, the period of the chiral helimagnetic ground state, which is proportional to the ratio between the ferromagnetic exchange and DM interactions, is smaller in $Cr_{1/3}TaS_2$ compared to $Cr_{1/3}NbS_2$.^{44,162} Thus, the interplay between different magnetic interactions results in these compounds having rich magnetic phase diagrams.^{40,134,163}

A remarkable find was made by Zhao *et al.*, who reported that self-intercalation of Ta, a nonmagnetic intercalant, in non-

magnetic TaS_2 and $TaSe_2$ can induce magnetic ordering at certain stoichiometries.¹³⁵ By intercalating $1/3$ of Ta in TaS_2 (*i.e.* Ta_7S_{12}), a ferromagnetic state was observed. Herein, the intercalated Ta atoms form a superlattice similar to those reported for $Fe_{1/3}MS_2$ and $Cr_{1/3}MS_2$ ($M = Nb, Ta$), in which the intercalated Ta atoms bond with six S atoms to form octahedral units (see Fig. 4(b)). DFT calculations showed that this additional bonding induces a charge transfer from the octahedrally-coordinated intercalated Ta atoms to the prismatic-coordinated Ta atoms of the host lattice. This induces a spin-split band close to the Fermi level, and causes a ferromagnetic ground state to form.¹³⁵ Hybridisation of the Ta $5d_{z^2}$ orbital with the spin-up band of the $5d_{x^2-y^2}$ orbital of the intercalated Ta causes the formation of this ferromagnetic ground state, where the magnetic moments are localised on the $5d$ orbitals of the intercalated Ta ions (see Figs. 4(c,d)).¹³⁵ Moreover, by intercalating $2/3$ of Ta in $TaSe_2$ (*i.e.* Ta_8Se_{12}), a Kagome lattice forms, which stabilises charge-density waves. Temperature-dependent Hall measurements revealed an anomalous Hall effect below 15 K, confirming the presence of ferromagnetic order.¹³⁵ This example again demonstrates the richness of induced physical phenomena that can be achieved by transition metal intercalation.

Furthermore, we note that despite the various reports on transition metal intercalation in transition metal dichalcogenides, little work has focused on intercalation of transition metals in other vdW magnets.

2.3 Molecule intercalation

In contrast to the above-mentioned alkali metal and transition metal intercalation, the use of molecular intercalants to tune the magnetic properties of vdW materials is relatively unexplored.



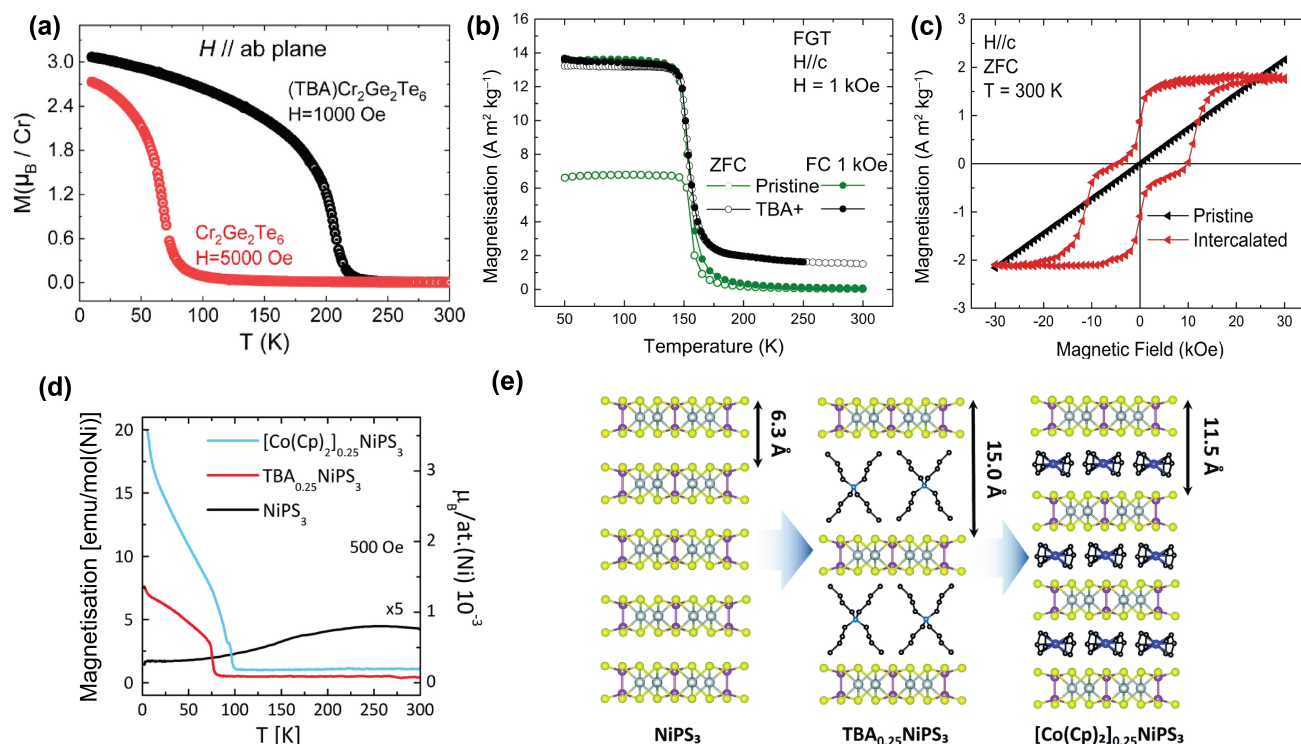


Fig. 5 TBA intercalation in magnetic vdW materials. (a) Temperature-dependent magnetisation of pristine $\text{Cr}_2\text{Ge}_2\text{Te}_6$ and TBA-intercalated $\text{Cr}_2\text{Ge}_2\text{Te}_6$ with H applied parallel to the ab -plane.³⁴ (b) Temperature-dependent magnetisation of pristine Fe_3GeTe_2 (green) and TBA-intercalated Fe_3GeTe_2 (black). Reproduced from ref. [32]. (c) Room-temperature, field-dependent magnetisation of pristine Fe_3GeTe_2 (black) and TBA-intercalated Fe_3GeTe_2 (red). Reproduced from ref. [32]. (d) Temperature-dependent magnetisation of pristine NiPS_3 (black), $\text{TBA}_{0.25}\text{NiPS}_3$ (red), and $[\text{Co}(\text{Cp})_2]_{0.25}\text{NiPS}_3$ (blue), measured in the ab -plane.³⁶ (e) Scheme of the intercalation of TBA cations in NiPS_3 , and the subsequent cation exchange with $\text{Co}(\text{Cp})_2^+$.³⁶ Reprinted with permission from ref. [34]. Copyright 2019 American Chemical Society. Reprinted from ref. [36] with permission from the Royal Society of Chemistry, copyright 2022.

However, molecules provide a particularly versatile platform for altering the properties of the host compound by means of intercalation, especially by tailoring the interlayer distance and charge density.¹⁶⁴

There are a few common methods employed to intercalate small molecules into vdW materials. The preferred method for alkylammonium cations is intercalation through electrochemical intercalation.^{32,34,36,165,166} For other molecular intercalants, a variety of chemical methods have typically been reported.^{167–171} Another method of intercalation is post-intercalation ion exchange, in which the host compound is first intercalated with another, easy-to-intercalate intercalant that is then replaced by the desired intercalant.^{36,172}

2.3.1 Alkylammonium cation intercalation

As molecules are typically much larger than monoatomic intercalants, they tend to increase the interlayer distance much more. To this end, alkylammonium cations have been widely investigated.^{32,34,36,165,166} Wang *et al.* intercalated $\text{Cr}_2\text{Ge}_2\text{Te}_6$ with tetrabutylammonium (TBA) cations, which increased the interlayer distance from 6.8 Å to 16.48 Å, consistent with inserting a single TBA cation layer of ~ 10 Å, without significantly influencing the in-plane lattice parameters.³⁴ Moreover, as shown in Fig. 5(a), they observed a massive increase in T_C from 67 K in pristine $\text{Cr}_2\text{Ge}_2\text{Te}_6$ to 208 K in the TBA-intercalated com-

pound. Besides this significant increase in T_C , TBA intercalation also changed the intrinsic magnetocrystalline anisotropy, reorienting the easy-axis from the c -axis in pristine $\text{Cr}_2\text{Ge}_2\text{Te}_6$ to lie in the ab -plane. In pristine $\text{Cr}_2\text{Ge}_2\text{Te}_6$, the spins mainly interact through 90° superexchange interactions via the Cr $3d_{z^2}$ and Te $5p$ orbitals.^{34,174,175} This results in weak ferromagnetic interlayer coupling and the easy-axis aligning with the c -axis due to spin-orbit coupling. DFT calculations on TBA-intercalated $\text{Cr}_2\text{Ge}_2\text{Te}_6$ showed that after intercalation, the $\text{Cr}_2\text{Ge}_2\text{Te}_6$ layers become electron-doped by the intercalant. These extra electrons were calculated to occupy the previously empty Cr $3d_{xy}$ and $3d_{yz}$ orbitals, resulting in a major density of state contribution near the Fermi level. As a result, the conducting electrons in the Cr $3d_{xy}$ and $3d_{yz}$ orbitals enable double exchange between the electron-doped Cr ions and the surrounding Cr ions that in combination with spin-orbit coupling causes the switch of the easy-axis.³⁴

In contrast, recent work by the Singamaneni group did not find any switching of the easy-axis upon intercalation of $\text{Cr}_2\text{Ge}_2\text{Te}_6$ with TBA.¹⁶⁶ They did, however, observe a similar change in exchange mechanism from superexchange to double exchange, as well as a previously reported semiconductor-to-metal ground state transition upon TBA intercalation.¹⁶⁶ This means that further work might be necessary to come to a clear conclusion regarding the easy-axis anisotropy.

In addition to TBA intercalation in $\text{Cr}_2\text{Ge}_2\text{Te}_6$, earlier work by



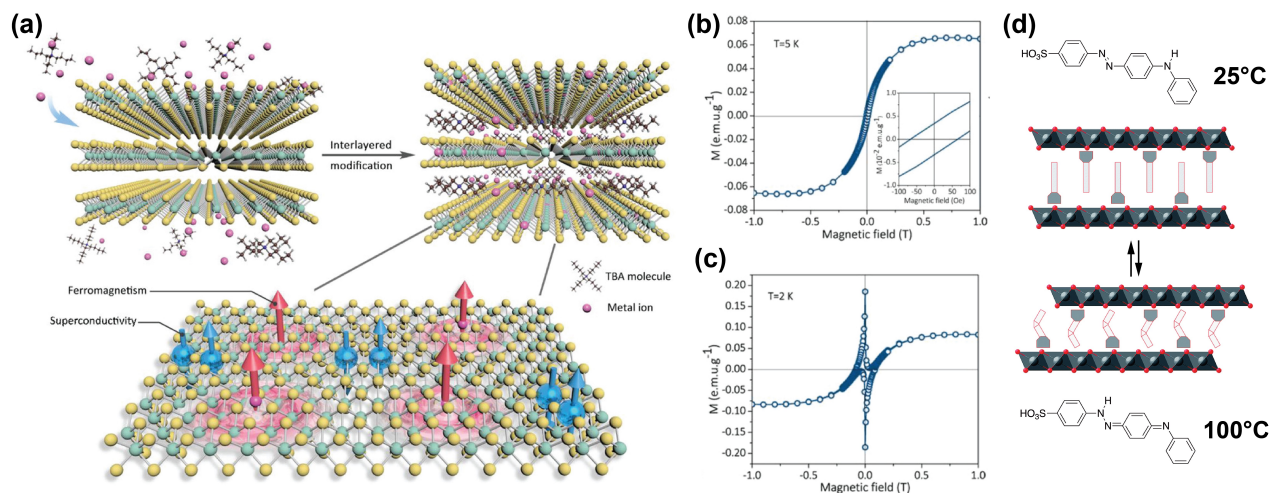


Fig. 6 (a) Schematic illustration of co-intercalation of TBA and Co ions in TaS_2 , creating an organic-inorganic superlattice with superconducting and ferromagnetic regions in a single atomic layer. Adapted from Li *et al.*¹⁷³ (b,c) Isothermal field-dependent magnetisation of Co and TBA-intercalated TaS_2 superlattice, at 5 K and 2 K.¹⁷³ (d) Schematic illustration of 4(4-anilinophenylazo)benzenesulfonate intercalated CoAl layered double hydroxides. The intercalant reversibly switches between the two isomers displayed at high and low temperatures, changing the interlayer distance. Reproduced from ref. [171]. Reproduced from ref. [173] with permission from John Wiley and Sons, copyright 2020.¹⁷¹

the same group showed that TBA intercalation in Fe_3GeTe_2 results in a negligible change in T_C (see Fig. 5(b)).³² Despite TBA not affecting T_C of Fe_3GeTe_2 ,^{30,32,176,177} it was suggested that charge transfer induced by intercalation results in the observation of room-temperature ferromagnetism.³² As shown in Fig. 5(c), this room-temperature ferromagnetism manifests itself as a ferromagnetic ‘wasp-waisted’ hysteresis loop, which can be indicative of competition between two different phases of different coercivities, in this case caused by antiferromagnetic exchange related to the antiferromagnetic interlayer coupling.³²

As shown in Fig. 5(d), intercalation of TBA into NiPS_3 to form $\text{TBA}_{0.25}\text{NiPS}_3$, on the other hand, suppresses the intrinsic antiferromagnetic order ($T_N = 155$ K) and instead induces ferrimagnetic order below ~ 78 K.³⁶ This change in magnetic ordering was argued to be caused by reducing Ni^{2+} cations in the host lattice to zerovalent Ni atoms, as a consequence of the electron doping by TBA. This reduction is accompanied by a displacement of the Ni ions from an octahedral to a tetrahedral coordination site, as confirmed by Raman measurements.³⁶ Since this only happens to a fraction of the Ni ions, the antiferromagnetic order is only partially suppressed, giving rise to the observed ferrimagnetic ordering.

Tezze *et al.* also reported on a substitution of the TBA cations with $(\text{Co}(\text{Cp})_2)^+$ through a non-redox cation exchange, utilizing the increased interlayer distance.³⁶ This exchange intercalation is illustrated in Fig. 5(e). The formed $[\text{Co}(\text{Cp})_2]_{0.25}\text{NiPS}_3$ also displays ferrimagnetic order, with an ordering temperature of ~ 98 K (see Fig. 5(d)). Note that this cation exchange could be applied more universally and provides a great template for studying molecular effects on the magnetic properties of the host lattice at a constant doping level.

2.3.2 Co-intercalation

The sizable increase in vdW gap between layers, induced by molecule intercalation, opens the door for simultaneous co-

intercalation of multiple intercalants. It was reported that co-intercalation aids in the intercalation of cations using metal ammonium solutions,^{80–82} although in these reactions the ammonium deintercalates again, leaving only the metal cations behind as intercalants. Co-intercalation of Li^+ and ammonia has shown to greatly enhance the interlayer spacing in Bi_2Se_3 ,¹⁷⁸ and increase the superconducting transition temperature in FeSe ,⁶⁶ but in this review we focus on tuning the magnetic properties of vdW materials and give an example of co-intercalation below.

Li *et al.* reported on co-intercalation of TBA cations with Co into the vdW gap of TaS_2 , introducing ferromagnetic long-range order whilst maintaining the superconductive properties of 2H-TaS_2 .¹⁷³ Intercalation of the TBA cations increased the vdW gap, and simultaneously allowed for surface modification by the Co ions, resulting in a TaS_2 organic-inorganic superlattice. The Co ions integrated into the basal plane of the TaS_2 layers, either by replacing Ta ions or by adsorbing into hollow sites in the layer, as shown in Fig. 6 (a).

The hysteresis loops shown in Figs. 6(b,c) reveal the presence of ferromagnetism at 5 K and both ferromagnetism and superconducting diamagnetism arising from the host lattice at 2 K.¹⁷³ DFT calculations showed that the integration of the Co ions introduced spin polarisation through orbital-specific hybridisation of the Co 3d orbitals with the Ta 5d and S 3p orbitals. The ferromagnetic coupling between the Co sites was also shown to be stronger than the antiferromagnetic coupling, resulting in the observed ferromagnetism. Because the majority spin density is localised on the Co sites, ferromagnetic coupling occurs through RKKY interactions, as the local magnetic moment could polarise the surrounding conduction electrons.¹⁷³

2.3.3 Molecule-derived functionality for tunable magnetic materials

Besides acting like a spacer or electron dopant, other properties of molecular intercalants can also be transferred to the host lat-



tice. In this way, molecular intercalation opens a pathway for exploring tunable magnetic systems with molecule-derived functionality, *e.g.* by using thermoresponsive, photoswitchable or chiral molecules, allowing for additional functionalisation of these materials.^{168,171,179}

One example of this was reported by Abellán *et al.*, who reported the intercalation of CoAl double hydroxide with 4(4-anilinophenylazo)benzenesulfonate; a thermoresponsive molecule which switches between two isomers depending on the temperature.¹⁷¹ Because the two isomers have different lengths, the interlayer distance of the intercalated compound can be reversibly switched between ~ 25.9 Å and ~ 25.1 Å by changing the temperature from 25 °C to 100 °C and back (see Fig. 6 (d)).

3 Materials chemistry challenges and opportunities

As described in the introduction, there is a large interest from the physics community in tuning the magnetic properties of vdW materials. The specific expertise of materials chemists is essential to enhance the field, not only by their ability to synthesise new compounds and perform (novel) intercalation reactions, but also by their characterisation toolkit necessary to study the produced materials in great detail. However, this comes with a number of challenges. In this section, we highlight the key challenges related to tuning magnetic properties of vdW materials by means of intercalation, and give directions for future research, calling on materials chemists to join this versatile field of research.

3.1 Determination of crystal structure and composition

To understand the effects of intercalation on the magnetic properties of the host lattice, a good understanding of any structural changes induced by intercalation is required. There are a variety of characterisation techniques that could be used to identify features of successful intercalation.^{52,104–107,180,181} The increased interlayer spacing obtained upon intercalation can be observed using X-ray diffraction (XRD) techniques, as peaks originating from the lateral planes normal to the stacking direction are expected to shift to lower angles. Moreover, this increased interlayer spacing can typically be observed using electron microscopy techniques. Lateral (scanning) transmission electron microscopy ((S)TEM) provides a sophisticated means to directly observe the increased layer spacing, and accurately determine the magnitude of this expansions.

The presence of both heavier elements, such as Te or I, found in a lot of magnetic vdW materials (*e.g.*, CrI₃, Fe₃GeTe₂ and Cr₂Ge₂Te₆), together with lighter elements such as Li poses a challenge for structural characterization using X-ray diffraction. In the presence of heavy elements that scatter X-rays strongly, the weak signal from the light intercalant species is diminished. Neutron scattering is the technique of choice to overcome this problem, as neutrons are sensitive to lighter elements as well.^{182,183} However, neutron scattering comes with additional challenges such as the need for large sample masses, typically in the order of grams, and access to large, international user facilities.

The structure determination using X-ray diffraction can also be

complicated by defects in the material. Particularly noteworthy defect are stacking faults – discontinuities in the stacking patterns of layered materials. These microstructural defects complicate structure determination, even at low concentration, because they affect both the intensities and shapes of the diffraction peaks in a non-trivial manner. This can make separating the contribution of stacking faults from other factors, such as occupational disorder and vacancies, very difficult. Moreover, it is crucial to mention that intercalated compounds can exhibit challenges with respect to their stability. Air-stability is often an issue, especially when small organic molecules are intercalated. This could lead to decomposition of the product. Furthermore, intercalation can also lead to exfoliation. While this can be used as a way to obtain monolayer products,¹⁸⁴ it also causes stability issues when searching for intercalated products.

Intercalants can also form superlattices.^{104,105,107,108,134,135} These can be directly captured using (S)TEM techniques,¹³⁵ or indirectly using selected area electron diffraction (SAED).^{104,107,135,155} The formation of superstructures also results in additional Bragg peaks in the diffraction patterns,^{52,104–107,113,185} and are often found in certain materials with more than 5% intercalation.^{105–107,113,186} Because defective superlattices are not necessarily apparent through X-ray diffraction alone, correlation of the magnetic (and electronic) properties using composition-determining techniques might be necessary.

Additional information about the structure of the intercalated material can be obtained through Raman scattering. Intercalation does not necessarily result in the observation of additional peaks with respect to the pristine host material, but an intercalated superlattice may reconstruct the Brillouin zone, giving rise to new phonons that may or may not be Raman active.⁵² The shifting of Raman peaks can be indicative of vibrational stiffening or softening due to electronic contributions from the intercalant. Raman scattering is especially useful in structure determination of molecular intercalation,^{32,36} as, in principle, no new Raman peaks are expected from metallic intercalants.

Aside from determining the changes to the host lattice, accurately determining the stoichiometry of the intercalated compound is of paramount importance, as magnetic properties are often highly sensitive to the degree of intercalation.^{31,37,41,134,135,153} Notably, not all studies investigate the precise composition by elemental analysis techniques, despite the fact that defective superlattices may not be apparent from diffraction. A precise report of composition and its correlation with magnetic and electronic properties may greatly improve the reproducibility.

Commonly available techniques to study the composition are energy-dispersive X-ray spectroscopy (EDX), X-ray fluorescence spectroscopy (XFS), X-ray photoelectron spectroscopy (XPS), energy electron loss spectroscopy (EELS) and inductively-coupled plasma analysis (ICP). However, these techniques may not always be sensitive enough to accurately determine concentrations of lighter elements. The development of muon elemental analysis, which is sensitive to problematic light elements such as Li, could be an outcome.^{187,188}



Electron microscopy can also be used to directly observe the intercalants. This is typically done through high-angle annular dark-field STEM. In practise this is done almost exclusively for transition metal intercalants,^{135,173} as the combination of light intercalant elements, such as Li or C and H present in organic molecules, and heavier elements typically present in the host lattice, results in low contrast due to the difference in scattering intensities between these different elements. This typically causes the lighter elements to be indistinguishable from the background noise. Techniques such as annular bright field STEM have allowed for the direct imaging of elements as light as hydrogen in other material systems, but require extremely thin samples (< 10 nm) to do so.¹⁸⁹ Molecular intercalants pose additional challenges in atomic resolution (S)TEM imaging due to the dynamics of the molecular intercalants and the potential for structural rearrangements.

Another crucial challenge is sample inhomogeneity. Intercalation typically starts at the edge of the vdW host material, before extending to the center of the flake with increasing intercalation time or amount.^{71,190,191} Moreover, optical microscopy studies have shown that diffusion within a single flake starts from the thick part of the flake and moves into the thin part.¹⁹¹ In-situ far-field optical techniques, including photoluminescence (PL) and Raman spectroscopy have been used to monitor electrochemical intercalation dynamics, but the light diffraction limit makes it difficult to exactly detect the distribution of intercalants with nanoscale resolution.⁵¹ Using in-situ TEM, the alkali-intercalation process was successfully probed with sub-nanoscale resolution, but the observed area was too small to be representative of the sample as a whole and determine its kinetics accurately. In addition, sample preparation for in-situ TEM measurements is a relatively complex and involved process.

3.2 Characterisation of magnetic properties

Determining the magnetic properties and magnetic structure of intercalated vdW materials is a non-trivial task. When assessing the magnetic properties of a sample, magnetic susceptibility measurements are often performed using SQUID magnetometry^{33,34,121,129,147,151,155,170,172} or vibrating-sample magnetometry (VSM).^{32,36,41,43,126} These techniques work well for *bulk* intercalated materials, but become problematic for few-layer samples. The same holds true for neutron scattering experiments that could be used to determine the magnetic ground state spin structure as well as its dynamics.^{127,130} As mentioned above, this requires large sample volumes and it cannot be used to determine spin structures of few-layer samples. Therefore, several other characterization techniques might be required. These techniques can be divided into optical techniques, electrical techniques, and electron microscopy techniques.

Optical spectroscopy is a powerful tool that can distinguish various types of magnetic ordering.¹⁹² A lot of pioneering work on 2D magnetism relied on the use of optical techniques.^{8–11,193} The most commonly used optical techniques are based on the magneto-optical Kerr effect (MOKE), which measures changes in polarisation of the interaction between linearly polarised light

and magnetism, and on magnetic circular dichroism (MCD), which measures the difference in absorption towards left- and right-handed light when incident polarised light passes through the sample under an external magnetic field.^{31,122,133,192} By measuring the polarisability or signal strength of the reflected light, MOKE can produce magnetisation curves. As the signal strength is proportional to the magnetisation, hysteresis loops can be obtained. The high spatial resolution also allows for obtaining information about domains and magnetisation processes.¹⁹² MCD allows for determining the magnetic state of a material by observing changes in amplitude and phase of the outgoing light. Limited by the measurement setup, MOKE and MCD are very sensitive to the magnetisation of a sample, but can only recognise out-of-plane magnetisation for few layer materials.

Electrical measurements on intercalated vdW materials typically take the form of Hall measurements.^{31,135,147} In ferromagnetic materials, both the normal Hall effect (NHE) and the anomalous Hall effect (AHE) exist, with the former being sensitive to the external magnetic field, and the latter dependent on the magnetisation of the sample. In vdW systems, the Hall resistance R_{xy} can be written as

$$R_{xy} = R_0 B_z + R_s M_z \quad (1)$$

where the first term denotes the normal Hall resistance, and the second term the anomalous Hall resistance. B_z and M_z denote the out-of-plane components of the applied magnetic field and magnetisation of the sample, respectively. R_0 and R_s are constants used to describe the strength of the NHE and AHE, respectively. In itinerant ferromagnets like Fe_3GeTe_2 , the NHE is negligibly weak compared to the AHE due to the metallic conductivity, allowing for straightforward characterisation of the ferromagnetism through AHE measurements.³¹ In these cases, R_{xy} is proportional to M_z , meaning that magnetisation can directly be obtained through measuring R_{xy} . Since most vdW magnets, as well as their intercalated counterparts, are insulators, in-plane transport measurements are almost impossible on many of these materials.

Aside from providing structural information, electron microscopy techniques can also be used to provide magnetic information about a sample, *e.g.* through Lorentz transmission electron microscopy (L-TEM). In L-TEM, when the electron beam passes through the sample, it is deflected by the Lorentz force of the intrinsic magnetic field of the sample. The detection of this beam then results in focusing and under-focusing which appear as black-and-white areas on a 2D map. This allows for the detection of exotic magnetic textures, and has been used to identify chiral helimagnetism⁴⁴ and skyrmions¹²¹ in intercalated vdW materials.

3.3 Future research directions

Based on the plethora of intercalation possibilities that can be exploited to tune the magnetic properties of vdW materials and the challenges that are associated with this, as highlighted in this review, we propose several directions for future research.

The number of vdW materials that have been successfully inter-



calated to tune their magnetic properties is relatively small compared to the rapidly increasing library of (magnetic) vdW materials. Given the topical nature of vdW materials research, more and more candidates for intercalation become rapidly available, while there simultaneously is a demand for materials with specific magnetic properties that can for example be implemented in spintronic applications.^{6,7} Therefore, materials chemists can play a crucial role in expanding the playing field by employing various types of intercalants, such as those described in section 2. This would give rise to magnetically-tunable materials with desired properties. For example, the tuning of magnetic properties through transition-metal intercalation has a strong focus on *3d* metals. With an increasing interest in exotic magnetic states originating from strong spin-orbit coupling,¹⁹⁴ the door is open for the exploration of intercalation of *4d*, *5d*, or possibly *4f* metals. Work by Koski and co-workers has shown that a good number of heavy metals can be readily intercalated,¹⁰⁴ but its relation to the magnetic properties is currently understudied.

Looking forward to spintronic applications, vdW materials play an essential role for hosting magnons, which form a key research direction within this field. However, investigation of magnons into intercalated vdW materials so far has been limited mainly to intercalated graphite.^{195–197} With the ever expanding library of (magnetic) vdW materials, and the broad range of intercalation possibilities highlighted in this review, new host lattices can be employed. Techniques such as Brillouin scattering (for acoustic magnons), Raman scattering (for optical magnons) and inelastic neutron scattering would need to be employed to successfully characterise magnons in these materials.

Until now, molecular intercalation has mainly focussed on the use of the intercalant as a dopant or spacer, with very little work utilizing other aspects of the versatile template that molecular intercalation forms. The use of molecule-derived functionalities could allow for responsive magnetic systems. These systems could, depending on the stimulus, tune their magnetic properties. This could be done by using thermoresponsive, photoswitchable, or chiral molecules.^{168,171,179} With molecular machines and more complex forms of soft matter gathering a lot of interest, one can envision complex, stimuli-responsive materials with reversibly tunable magnetic interactions.

Another relatively underexplored area is that of using multiple functionalities of intercalants in one system. For example, Chen *et al.* successfully intercalated dual elements into Be₂Se₃, resulting in the formation of superlattices.¹⁰⁷ This could form a platform for complex novel magnetic structures that can further expand the field of magnetic-property tuning by means of chemical intercalation. As demonstrated by Li *et al.*, co-functionality can extend beyond the need of two similar intercalants, as combining multiple families of intercalants opens up the avenue for new types of intercalated compounds that combine their functionalities into a single host lattice.¹⁷³

Moreover, a lot of intercalated vdW materials are not (air) stable. For these materials to be used in device application, this barrier needs to be overcome. This can be done either by formation of air stable intercalants, or by exploring methods to encapsulating the intercalated products. So far, this has barely been

explored.

Another research direction that would require enhanced efforts is the understanding of the intercalation process. Especially with regards to the dynamics of intercalation, a lot is still left unknown. To this end, several in-situ studies have been performed, using optical microscopy,¹⁹⁰ and X-ray and neutron scattering techniques.¹⁷⁸ Understanding the dynamics can give us insights into the intercalation process and inhomogeneity, allowing for a better prediction of the formed intercalation products and their properties.

Aside from using intercalation to tune the (magnetic) properties of vdW materials, intercalation has also been employed to exfoliate layered materials. Compared to other top-down exfoliation techniques, such as micromechanical cleavage¹ and direct liquid exfoliation,¹⁹⁸ intercalation-based exfoliation results in high yields of exfoliation and is applicable to a wide range of vdW materials.^{184,199} A recent review by Yang *et al.* extensively describes several intercalation-based exfoliation strategies and provides a great overview of the status quo. We therefore refer the reader to this review for additional information and future research directions along the line of exfoliation.¹⁸⁴

4 Conclusion

VdW materials have gained a lot of interest from the solid-state community, and there is a specific interest in vdW materials with tunable magnetic properties. In this review, we have provided a comprehensive overview of the most common forms of intercalation reactions that are used to achieve this goal. While alkali metal intercalation is potentially the most studied form of intercalation, we also pinpointed the various exotic changes observed by transition metal intercalation. Moreover, we discussed how molecule intercalation embodies a rather versatile, yet underexplored, area in the field. Furthermore, we have highlighted the most common materials chemistry challenges and opportunities that could enhance the field. These challenges are based on accurately determining the materials structure and composition, as well as on characterising the magnetic properties. In this review we proposed future research directions along the lines of exploring other forms of intercalation, *e.g.* heavy-metal intercalation, molecule intercalation and intercalating multiple functionalities into a single host lattice, as well as for investigating air-stability and understanding the intercalation mechanism in more detail. We are certain that the expertise of materials chemists is crucial to enhance this field.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

MEK acknowledges the research program “Materials for the Quantum Age” (QuMat) for financial support. This program (registration number 024.005.006) is part of the Gravitation program financed by the Dutch Ministry of Education, Culture and Science (OCW).



References

- (1) K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, *Science*, 2004, **306**, 666–669, DOI: 10.1126/science.1102896.
- (2) A. K. Geim and I. V. Grigorieva, *Nature*, 2013, **499**, 419–425, DOI: 10.1038/nature12385.
- (3) G. Fiori, F. Bonaccorso, G. Iannaccone, T. Palacios, D. Neumaier, A. Seabaugh, S. K. Banerjee and L. Colombo, *Nature Nanotechnology*, 2014, **9**, 768–779, DOI: 10.1038/nnano.2014.207.
- (4) J. G. Park, *Journal of Physics Condensed Matter*, 2016, **28**, DOI: 10.1088/0953-8984/28/30/301001.
- (5) S. Manzeli, D. Ovchinnikov, D. Pasquier, O. V. Yazyev and A. Kis, *Nature Reviews Materials*, 2017, **2**, DOI: 10.1038/natrevmats.2017.33.
- (6) N. Samarth, *Nature*, 2017, **546**, 216–218, DOI: 10.1038/546216a.
- (7) K. S. Burch, D. Mandrus and J. G. Park, *Nature*, 2018, **563**, 47–52, DOI: 10.1038/s41586-018-0631-z.
- (8) J. U. Lee, S. Lee, J. H. Ryoo, S. Kang, T. Y. Kim, P. Kim, C. H. Park, J. G. Park and H. Cheong, *Nano Letters*, 2016, **16**, 7433–7438, DOI: 10.1021/acs.nanolett.6b03052.
- (9) C. Gong, L. Li, Z. Li, H. Ji, A. Stern, Y. Xia, T. Cao, W. Bao, C. Wang, Y. Wang, Z. Q. Qiu, R. J. Cava, S. G. Louie, J. Xia and X. Zhang, *Nature*, 2017, **546**, 265–269, DOI: 10.1038/nature22060.
- (10) B. Huang, G. Clark, E. Navarro-Moratalla, D. R. Klein, R. Cheng, K. L. Seyler, D. Zhong, E. Schmidgall, M. A. McGuire, D. H. Cobden, W. Yao, D. Xiao, P. Jarillo-Herrero and X. Xu, *Nature*, 2017, **546**, 270–273, DOI: 10.1038/nature22391.
- (11) B. Huang, G. Clark, D. R. Klein, D. MacNeill, E. Navarro-Moratalla, K. L. Seyler, N. Wilson, M. A. McGuire, D. H. Cobden, D. Xiao, W. Yao, P. Jarillo-Herrero and X. Xu, *Nature Nanotechnology*, 2018, **13**, 544–548, DOI: 10.1038/s41565-018-0121-3.
- (12) S. Yang, T. Zhang and C. Jiang, *Advanced Science*, 2021, **8**, DOI: 10.1002/advs.202002488.
- (13) H. Wang, V. Eyert and U. Schwingenschlögl, *Journal of Physics Condensed Matter*, 2011, **23**, DOI: 10.1088/0953-8984/23/11/116003.
- (14) T. Kong, K. Stolze, E. I. Timmons, J. Tao, D. Ni, S. Guo, Z. Yang, R. Prozorov and R. J. Cava, *Advanced Materials*, 2019, **31**, 1808074, DOI: 10.1002/adma.201808074.
- (15) B. Zhang, Y. Zeng, Z. J. Zhao, D. P. Qiu, T. Zhang and Y. L. Hou, *Rare Metals*, 2022, **41**, 2921–2942, DOI: 10.1007/s12598-022-02004-2.
- (16) S. Mondal, A. Midya, M. M. Patidar, V. Ganesan and P. Mandal, *Applied Physics Letters*, 2020, **117**, DOI: 10.1063/5.0019985.
- (17) M. Bonilla, S. Kolekar, Y. Ma, H. C. Diaz, V. Kalappattil, R. Das, T. Eggers, H. R. Gutierrez, M. H. Phan and M. Batzill, *Nature Nanotechnology*, 2018, **13**, 289–293, DOI: 10.1038/s41565-018-0063-9.
- (18) B. Li, Z. Wan, C. Wang, P. Chen, B. Huang, X. Cheng, Q. Qian, J. Li, Z. Zhang, G. Sun, B. Zhao, H. Ma, R. Wu, Z. Wei, Y. Liu, L. Liao, Y. Ye, Y. Huang, X. Xu, X. Duan, W. Ji and X. Duan, *Nature Materials*, 2021, **20**, 818–825, DOI: 10.1038/s41563-021-00927-2.
- (19) Y. Zhang, J. Chu, L. Yin, T. A. Shifa, Z. Cheng, R. Cheng, F. Wang, Y. Wen, X. Zhan, Z. Wang and J. He, *Advanced Materials*, 2019, **31**, DOI: 10.1002/adma.201900056.
- (20) G. Le Flem, R. Brec, G. Ouvard, A. L. uisy and P. Segransan, *Journal of Physics and Chemistry of Solids*, 1982, **43**, 455–461, DOI: 10.1016/0022-3697(82)90156-1.
- (21) Y. Peng, S. Ding, M. Cheng, Q. Hu, J. Yang, F. Wang, M. Xue, Z. Liu, Z. Lin, M. Avdeev, Y. Hou, W. Yang, Y. Zheng and J. Yang, *Advanced Materials*, 2020, **32**, DOI: 10.1002/adma.202001200.
- (22) Y. J. Sun, Q. H. Tan, X. L. Liu, Y. F. Gao and J. Zhang, *Journal of Physical Chemistry Letters*, 2019, **10**, 3087–3093, DOI: 10.1021/acs.jpcllett.9b00758.
- (23) T. Zhang, Y. Wang, H. Li, F. Zhong, J. Shi, M. Wu, Z. Sun, W. Shen, B. Wei, W. Hu, X. Liu, L. Huang, C. Hu, Z. Wang, C. Jiang, S. Yang, Q. M. Zhang and Z. Qu, *ACS Nano*, 2019, **13**, 11353–11362, DOI: 10.1021/acsnano.9b04726.
- (24) W. Wang, R. Sun, S. He, Z. Jia, C. Su, Y. Li and Z. Wang, *2D Materials*, 2021, **8**, 015027, DOI: 10.1088/2053-1583/abc5cf.
- (25) J. Klein, T. Pham, J. D. Thomsen, J. B. Curtis, T. Deneulin, M. Lorke, M. Florian, A. Steinhoff, R. A. Wiscons, J. Luxa, Z. Sofer, F. Jahnke, P. Narang and F. M. Ross, *Nature Communications*, 2022, **13**, DOI: 10.1038/s41467-022-32737-8.
- (26) K. Lee, A. H. Dismukes, E. J. Telford, R. A. Wiscons, J. Wang, X. Xu, C. Nuckolls, C. R. Dean, X. Roy and X. Zhu, *Nano Letters*, 2021, **21**, 3511–3517, DOI: 10.1021/acs.nanolett.1c00219.
- (27) M. E. Ziebel, M. L. Feuer, J. Cox, X. Zhu, C. R. Dean and X. Roy, *CrSBr: An Air-Stable, Two-Dimensional Magnetic Semiconductor*, 2024, DOI: 10.1021/acs.nanolett.4c00624.
- (28) X. Zhang, Q. Lu, W. Liu, W. Niu, J. Sun, J. Cook, M. Vaninger, P. F. Miceli, D. J. Singh, S. W. Lian, T. R. Chang, X. He, J. Du, L. He, R. Zhang, G. Bian and Y. Xu, *Nature Communications*, 2021, **12**, DOI: 10.1038/s41467-021-22777-x.



- (29) G. Zhang, F. Guo, H. Wu, X. Wen, L. Yang, W. Jin, W. Zhang and H. Chang, *Nature Communications*, 2022, **13**, DOI: 10.1038/s41467-022-32605-5.
- (30) A. F. May, S. Calder, C. Cantoni, H. Cao and M. A. McGuire, *Physical Review B*, 2016, **93**, DOI: 10.1103/PhysRevB.93.014411.
- (31) Y. Deng, Y. Yu, Y. Song, J. Zhang, N. Z. Wang, Z. Sun, Y. Yi, Y. Z. Wu, S. Wu, J. Zhu, J. Wang, X. H. Chen and Y. Zhang, *Nature*, 2018, **563**, 94–99, DOI: 10.1038/s41586-018-0626-9.
- (32) H. Iturriaga, L. M. Martinez, T. T. Mai, A. J. Biacchi, M. Augustin, A. R. Hight Walker, M. F. Sanad, S. T. Sreenivasan, Y. Liu, E. J. Santos, C. Petrovic and S. R. Singamaneni, *npj 2D Materials and Applications*, 2023, **7**, DOI: 10.1038/s41699-023-00417-w.
- (33) S. Khan, E. S. Y. Aw, L. A. V. Nagle-Cocco, A. Sud, S. Ghosh, M. K. B. Subhan, Z. Xue, C. Freeman, D. Sagkovits, A. Gutierrez-Llorente, I. Verzhbitskiy, D. M. Arroo, C. W. Zollitsch, G. Eda, E. J. G. Santos, S. E. Dutton, S. T. Bramwell, C. A. Howard and H. Kurebayashi, *arXiv*, 2023, DOI: 10.48550/arXiv.2312.17554.
- (34) N. Wang, H. Tang, M. Shi, H. Zhang, W. Zhuo, D. Liu, F. Meng, L. Ma, J. Ying, L. Zou, Z. Sun and X. Chen, *Journal of the American Chemical Society*, 2019, **141**, 17166–17173, DOI: 10.1021/jacs.9b06929.
- (35) P. A. Joy and S. Vasudevan, *PHYSICAL REVIEW B*, 1992, **46**, DOI: 10.1103/PhysRevB.46.5425.
- (36) D. Tezze, J. M. Pereira, Y. Asensio, M. Ipatov, F. Calavalle, F. Casanova, A. M. Bittner, M. Ormaza, B. Martín-García, L. E. Hueso and M. Gobbi, *Nanoscale*, 2022, **14**, 1165–1173, DOI: 10.1039/d1nr07281a.
- (37) O. Gorochov, A. Le Blanc-Soreau, J. Rouxel, P. Imbert and G. Jehanno, *Philosophical Magazine B: Physics of Condensed Matter; Statistical Mechanics, Electronic, Optical and Magnetic Properties*, 1981, **43**, 621–634, DOI: 10.1080/01418638108222164.
- (38) Y. Yamamura, S. Moriyama, T. Tsuji, Y. Iwasa, M. Koyano, S. Katayama and M. Ito, *Journal of Alloys and Compounds*, 2004, **383**, 338–341, DOI: 10.1016/j.jallcom.2004.04.045.
- (39) T. Miyadai, K. Kikuchi, H. Kondo, S. Sakka, M. Arai and Y. Ishikawa, *Journal of the Physical Society Japan*, 1983, **52**, 1394–1401, DOI: 10.1143/JPSJ.52.1394.
- (40) H. Han, L. Zhang, D. Sapkota, N. Hao, L. Ling, H. Du, L. Pi, C. Zhang, D. G. Mandrus and Y. Zhang, *Physical Review B*, 2017, **96**, DOI: 10.1103/PhysRevB.96.094439.
- (41) C. W. Chen, S. Chikara, V. S. Zapf and E. Morosan, *Physical Review B*, 2016, **94**, DOI: 10.1103/PhysRevB.94.054406.
- (42) E. Morosan, H. W. Zandbergen, L. Li, M. Lee, J. G. Checkelsky, M. Heinrich, T. Siegrist, N. P. Ong and R. J. Cava, *Physical Review B - Condensed Matter and Materials Physics*, 2007, **75**, DOI: 10.1103/PhysRevB.75.104401.
- (43) S. Mangelsen, J. Hansen, P. Adler, W. Schnelle, W. Bensch, S. Mankovsky, S. Polesya and H. Ebert, *Journal of Physical Chemistry C*, 2020, **124**, 24984–24994, DOI: 10.1021/acs.jpcc.0c07711.
- (44) C. Zhang, J. Zhang, C. Liu, S. Zhang, Y. Yuan, P. Li, Y. Wen, Z. Jiang, B. Zhou, Y. Lei, D. Zheng, C. Song, Z. Hou, W. Mi, U. Schwingenschlögl, A. Manchon, Z. Q. Qiu, H. N. Alshareef, Y. Peng and X. X. Zhang, *Advanced Materials*, 2021, **33**, DOI: 10.1002/adma.202101131.
- (45) D. C. Freitas, R. Weht, A. Sulpice, G. Remenyi, P. Strobel, F. Gay, J. Marcus and M. Núñez-Regueiro, *Journal of Physics Condensed Matter*, 2015, **27**, DOI: 10.1088/0953-8984/27/17/176002.
- (46) A. L. Coughlin, D. Xie, X. Zhan, Y. Yao, L. Deng, H. Hewa-Walpitage, T. Bontke, C. W. Chu, Y. Li, J. Wang, H. A. Fertig and S. Zhang, *Nano Letters*, 2021, **21**, 9517–9525, DOI: 10.1021/acs.nanolett.1c02940.
- (47) M. Yamaguchi and T. Hashimoto, *Journal of the Physical Society of Japan*, 1972, **32**, 635–638, DOI: doi.org/10.1143/JPSJ.32.635.
- (48) M. A. McGuire, H. Dixit, V. R. Cooper and B. C. Sales, *Chemistry of Materials*, 2015, **27**, 612–620, DOI: 10.1021/cm504242t.
- (49) O. Gisser, W. Paul and H. G. Kahle, *Journal of Magnetism and Magnetic Materials*, 1990, **92**, 129, DOI: 10.1016/0304-8853(90)90689-N.
- (50) M. Rajapakse, B. Karki, U. O. Abu, S. Pishgar, M. R. K. Musa, S. M. Riyadh, M. Yu, G. Sumanasekera and J. B. Jasinski, *npj 2D Materials and Applications*, 2021, **5**, DOI: 10.1038/s41699-021-00211-6.
- (51) Y. Li, H. Yan, B. Xu, L. Zhen and C. Y. Xu, *Advanced Materials*, 2021, **33**, DOI: 10.1002/adma.202000581.
- (52) M. S. Dresselhaus, *Intercalation in layered materials; NATO ASI Series, Subseries B, Physics*, Plenum Press, New York, 1987.
- (53) W. Müller-Warmuth and R. Schöllhorn, *Progress in Intercalation Research*, ed. W. Müller-Warmuth and R. Schöllhorn, Springer Netherlands, Dordrecht, 1994, vol. 17, DOI: 10.1007/978-94-011-0890-4.
- (54) M. S. Whittingham, *Science*, 1976, **192**, 1126–1127, DOI: 10.1126/science.192.4244.1126.
- (55) W. B. Johnson and W. L. Worrell, *Synthetic Metals*, 1982, **4**, 225–248, DOI: 10.1016/0379-6779(82)90015-7.
- (56) D. Li, D. L. Danilov, L. Gao, Y. Yang and P. H. L. Notten, *Journal of The Electrochemical Society*, 2016, **163**, A3016–A3021, DOI: 10.1149/2.0821614jes.
- (57) M. Winter, B. Barnett and K. Xu, *Chemical Reviews*, 2018, **118**, 11433–11456, DOI: 10.1021/acs.chemrev.8b00422.



- (58) Y. Gu, Y. Katsura, T. Yoshino, H. Takagi and K. Taniguchi, *Scientific Reports*, 2015, **5**, DOI: 10.1038/srep12486.
- (59) V. Augustyn, J. Come, M. A. Lowe, J. W. Kim, P. L. Taberna, S. H. Tolbert, H. D. Abruña, P. Simon and B. Dunn, *Nature Materials*, 2013, **12**, 518–522, DOI: 10.1038/nmat3601.
- (60) M. R. Lukatskaya, B. Dunn and Y. Gogotsi, *Nature Communications*, 2016, **7**, DOI: 10.1038/ncomms12647.
- (61) Y. Koike, H. Suematsu, K. Higuchi and S. Tanuma, *Solid State Communications*, 1978, **27**, 623–627, DOI: 10.1016/0038-1098(78)90457-X.
- (62) T. E. Weller, M. Ellerb, S. S. Saxena, R. P. Smith and N. T. Skipper, *Nature Physics*, 2005, **1**, 39–41, DOI: 10.1038/nphys0010.
- (63) J. T. Ye, Y. J. Zhang, R. Akashi, M. S. Bahramy, R. Arita and Y. Iwasa, *Science*, 2012, **338**, 1193–1196, DOI: 10.1126/science.1228006.
- (64) Y. Saito, Y. Kasahara, J. Ye, Y. Iwasa and T. Nojima, *Science*, 2015, **350**, 409–413, DOI: 10.1126/science.1259440.
- (65) N. Z. Wang, M. Z. Shi, C. Shang, F. B. Meng, L. K. Ma, X. G. Luo and X. H. Chen, *New Journal of Physics*, 2018, **20**, 023014, DOI: 10.1088/1367-2630/aaa8a7.
- (66) M. Burrard-Lucas, D. G. Free, S. J. Sedlmaier, J. D. Wright, S. J. Cassidy, Y. Hara, A. J. Corkett, T. Lancaster, P. J. Baker, S. J. Blundell and S. J. Clarke, *Nature Materials*, 2013, **12**, 15–19, DOI: 10.1038/nmat3464.
- (67) E. Morosan, H. W. Zandbergen, B. S. Dennis, J. W. Bos, Y. Onose, T. Klimczuk, A. P. Ramirez, N. P. Ong and R. J. Cava, *Nature Physics*, 2006, **2**, 544–550, DOI: 10.1038/nphys360.
- (68) C. Pettenkofer and W. Jaegermann, *Physical Review B*, 1994, **50**, 8816–8823, DOI: 10.1103/PhysRevB.50.8816.
- (69) K. E. Wagner, E. Morosan, Y. S. Hor, J. Tao, Y. Zhu, T. Sanders, T. M. McQueen, H. W. Zandbergen, A. J. Williams, D. V. West and R. J. Cava, *Physical Review B*, 2008, **78**, 104520, DOI: 10.1103/PhysRevB.78.104520.
- (70) M. Wang and K. J. Koski, *ACS Nano*, 2015, **9**, 3226–3233, DOI: 10.1021/acs.nano.5b00336.
- (71) F. Xiong, H. Wang, X. Liu, J. Sun, M. Brongersma, E. Pop and Y. Cui, *Nano Letters*, 2015, **15**, 6777–6784, DOI: 10.1021/acs.nanolett.5b02619.
- (72) L. Quan, H. Zhang, H. Wei, Y. Li, S. O. Park, D. Y. Hwang, Y. Tian, M. Huang, C. Wang, M. Wang, S. K. Kwak, F. Qin, H. X. Peng and R. S. Ruoff, *ACS Applied Materials and Interfaces*, 2020, **12**, 16841–16848, DOI: 10.1021/acami.0c02301.
- (73) E. Guilmeau, Y. Bréard and A. Maignan, *Applied Physics Letters*, 2011, **99**, DOI: 10.1063/1.3621834.
- (74) R. Matsumoto, Y. Okabe and N. Akuzawa, *Journal of Electronic Materials*, 2015, **44**, 399–406, DOI: 10.1007/s11664-014-3409-6.
- (75) G. Zhu, J. Liu, Q. Zheng, R. Zhang, D. Li, D. Banerjee and D. G. Cahill, *Nature Communications*, 2016, **7**, DOI: 10.1038/ncomms13211.
- (76) J. S. Kang, M. Ke and Y. Hu, *Nano Letters*, 2017, **17**, 1431–1438, DOI: 10.1021/acs.nanolett.6b04385.
- (77) X. Huang, J. Xu, R. Zeng, Q. Jiang, X. Nie, C. Chen, X. Jiang and J. M. Liu, *Applied Physics Letters*, 2021, **119**, DOI: 10.1063/5.0051882.
- (78) D. Weber, A. H. Trout, D. W. McComb and J. E. Goldberger, *Nano Letters*, 2019, **19**, 5031–5035, DOI: 10.1021/acs.nanolett.9b01287.
- (79) H. M. Ahamd and J. Zhou, *AIP Advances*, 2020, **10**, DOI: 10.1063/1.5139061.
- (80) W. Rüdorff, *Angewandte Chemie*, 1959, **71**, 487–491, DOI: 10.1002/ange.19590711504.
- (81) R. B. Somoano, V. Hadek and A. Rembaum, *The Journal of Chemical Physics*, 1973, **58**, 697–701, DOI: 10.1063/1.1679256.
- (82) J. A. Woollam and R. B. Somoano, *Materials Science and Engineering*, 1977, **31**, 289–295, DOI: 10.1016/0025-5416(77)90048-9.
- (83) P. Palvadeau, L. Coïc, J. Rouxel and J. Portier, *Mat. Res. Bul.*, 1978, **13**, 221–227, DOI: 10.1016/0025-5408(78)90226-X.
- (84) M. B. Dines, *Materials Research Bulletin*, 1975, **10**, 287–292, DOI: 10.1016/0025-5408(75)90115-4.
- (85) D. W. Murphy, J. Di Salvo, Francis, G. W. Hull and J. V. Waszczak, *Inorganic Chemistry*, 1976, **15**, 17–21, DOI: 10.1021/ic50155a005.
- (86) C. Berthier, Y. Chabre and M. Minier, *Solid State Communications*, 1978, **28**, 327–332, DOI: 10.1016/0038-1098(78)90434-9.
- (87) H.-L. Tsai, J. Heising, J. L. Schindler, C. R. Kannewurf and M. G. Kanatzidis, *Chemistry of Materials*, 1997, **21**, 879–882, DOI: 10.1021/cm960579t.
- (88) X. Zhu, Z. Su, C. Wu, H. Cong, X. Ai, H. Yang and J. Qian, *Nano Letters*, 2022, **22**, 2956–2963, DOI: 10.1021/acs.nanolett.2c00148.
- (89) A. M. Ferrenti, S. Klemenz, S. Lei, X. Song, P. Ganter, B. V. Lotsch and L. M. Schoop, *Inorganic Chemistry*, 2020, **59**, 1176–1182, DOI: 10.1021/acs.inorgchem.9b02856.
- (90) G. Villalpando, A. M. Ferrenti, R. Singha, X. Song, G. Cheng, N. Yao and L. M. Schoop, *ACS Nano*, 2022, **16**, 13814–13820, DOI: 10.1021/acsnano.2c01858.
- (91) J. Zheng, H. Zhang, S. Dong, Y. Liu, C. Tai Nai, H. Suk Shin, H. Young Jeong, B. Liu and K. Ping Loh, *Nature Communications*, 2014, **5**, DOI: 10.1038/ncomms3995.



- (92) A. I. Smith, H. V. Wladkowski, Z. H. Hecht, Y. She, S. Kattel, P. I. Samarawickrama, S. R. Rich, J. R. Murphy, J. Tian, J. F. Ackerman, W. D. Rice, E. B. Hulley and B. M. Leonard, *Chemistry of Materials*, 2020, **32**, 10482–10488, DOI: 10.1021/acs.chemmater.0c03270.
- (93) Y. Yu, F. Yang, X. F. Lu, Y. J. Yan, Y. H. Cho, L. Ma, X. Niu, S. Kim, Y. W. Son, D. Feng, S. Li, S. W. Cheong, X. H. Chen and Y. Zhang, *Nature Nanotechnology*, 2015, **10**, 270–276, DOI: 10.1038/nnano.2014.323.
- (94) Y. Guo, R. B. Smith, Z. Yu, D. K. Efetov, J. Wang, P. Kim, M. Z. Bazant and L. E. Brus, *Journal of Physical Chemistry Letters*, 2016, **7**, 2151–2156, DOI: 10.1021/acs.jpcclett.6b00625.
- (95) Y. Wu, J. He, J. Liu, H. Xing, Z. Mao and Y. Liu, *Nanotechnology*, 2019, **30**, DOI: 10.1088/1361-6528/a9a3b.
- (96) D. K. Bediako, M. Rezaee, H. Yoo, D. T. Larson, S. Y. Zhao, T. Taniguchi, K. Watanabe, T. L. Brower-Thomas, E. Kaxiras and P. Kim, *Nature*, 2018, **558**, 425–429, DOI: 10.1038/s41586-018-0205-0.
- (97) L. Oakes, R. Carter, T. Hanken, A. P. Cohn, K. Share, B. Schmidt and C. L. Pint, *Nature Communications*, 2016, **7**, DOI: 10.1038/ncomms11796.
- (98) R. Basnet, D. Ford, K. Tenbarger, J. Lochala and J. Hu, *Journal of Physics Condensed Matter*, 2022, **34**, DOI: 10.1088/1361-648X/ac8a81.
- (99) D. Wu, Y. Zhao, Y. Yang, L. Huang, Y. Xiao, S. Chen and Y. Zhao, *Nanomaterials*, 2022, **12**, DOI: 10.3390/nano12091420.
- (100) A. Kabiraj and S. Mahapatra, *Journal of Physical Chemistry C*, 2020, **124**, 1146–1157, DOI: 10.1021/acs.jpcc.9b09477.
- (101) Z.-X. Shen, X. Bo, K. Cao, X. Wan and L. He, *Physical Review B*, 2021, **108**, DOI: 10.1103/PhysRevB.108.085102.
- (102) Y. Ma, Y. Dai, M. Guo, C. Niu, Y. Zhu and B. Huang, *ACS Nano*, 2012, **6**, 1695–1701, DOI: 10.1021/nn204667z.
- (103) H. R. Fuh, B. Yan, S. C. Wu, C. Felser and C. R. Chang, *New Journal of Physics*, 2016, **18**, DOI: 10.1088/1367-2630/18/11/113038.
- (104) M. Wang, D. Williams, G. Lahti, S. Teshima, D. D. Aguilar, R. Perry and K. J. Koski, *2D Materials*, 2018, **5**, DOI: 10.1088/2053-1583/aacf2.
- (105) K. J. Koski, C. D. Wessells, B. W. Reed, J. J. Cha, D. Kong and Y. Cui, *Journal of the American Chemical Society*, 2012, **134**, 13773–13779, DOI: 10.1021/ja304925t.
- (106) K. J. Koski, J. J. Cha, B. W. Reed, C. D. Wessells, D. Kong and Y. Cui, *Journal of the American Chemical Society*, 2012, **134**, 7584–7587, DOI: 10.1021/ja300368x.
- (107) K. P. Chen, F. R. Chung, M. Wang and K. J. Koski, *Journal of the American Chemical Society*, 2015, **137**, 5431–5437, DOI: 10.1021/jacs.5b00666.
- (108) J. P. Motter, K. J. Koski and Y. Cui, *Chemistry of Materials*, 2014, **26**, 2313–2317, DOI: 10.1021/cm500242h.
- (109) Y. Gong, H. Yuan, C. L. Wu, P. Tang, S. Z. Yang, A. Yang, G. Li, B. Liu, J. Van De Groep, M. L. Brongersma, M. F. Chisholm, S. C. Zhang, W. Zhou and Y. Cui, *Nature Nanotechnology*, 2018, **13**, 294–299, DOI: 10.1038/s41565-018-0069-3.
- (110) E. W. Ong, M. J. McKelvy, G. Ouvrard, W. S. Glaunsinger and V. Dreele, *Chemistry of Materials*, 1992, **4**, 14–17, DOI: 10.1021/cm00019a006.
- (111) M. V. Sidorovw, M. J. Mckelvy, R. Sharma and W. S. Glaunsinger, *Journal of Solid State Chemistry*, 1998, **141**, 330–337, DOI: 10.1006/jssc.1998.7929.
- (112) Z. Li, D. Li, H. Wang, P. Chen, L. Pi, X. Zhou and T. Zhai, *Small Methods*, 2021, **5**, 2100567, DOI: 10.1002/smt.d.202100567.
- (113) M. Wang, I. Al-Dhahir, J. Appiah and K. J. Koski, *Chemistry of Materials*, 2017, **29**, 1650–1655, DOI: 10.1021/acs.chemmater.6b04918.
- (114) H. Narita, H. Ikuta, H. Hinode, T. Uchida, T. Ohtani and M. Wakihara, *Journal of Solid State Chemistry*, 1994, **108**, 148–151, DOI: 10.1006/jssc.1994.1022.
- (115) Y. Fujisawa, M. Pardo-Almanza, J. Garland, K. Yamagami, X. Zhu, X. Chen, K. Araki, T. Takeda, M. Kobayashi, Y. Takeda, C. H. Hsu, F. C. Chuang, R. Laskowski, K. H. Khoo, A. Soumyanarayanan and Y. Okada, *Physical Review Materials*, 2020, **4**, 114001, DOI: 10.1103/PhysRevMaterials.4.114001.
- (116) X. Sun, W. Li, X. Wang, Q. Sui, T. Zhang, Z. Wang, L. Liu, D. Li, S. Feng, S. Zhong, H. Wang, V. Bouchiat, M. Nunez Regueiro, N. Rougemaille, J. Coraux, A. Purbawati, A. Hadj-Azzem, Z. Wang, B. Dong, X. Wu, T. Yang, G. Yu, B. Wang, Z. Han, X. Han and Z. Zhang, *Nano Research*, 2020, **13**, 3358–3363, DOI: 10.1007/s12274-020-3021-4.
- (117) Y. Liu and C. Petrovic, *Physical Review B*, 2017, **96**, DOI: 10.1103/PhysRevB.96.134410.
- (118) Y. Liu and C. Petrovic, *Physical Review B*, 2018, **98**, DOI: 10.1103/PhysRevB.98.195122.
- (119) Y. Liu, M. Abeykoon, E. Stavitski, K. Attenkofer and C. Petrovic, *Physical Review B*, 2019, **100**, DOI: 10.1103/PhysRevB.100.245114.
- (120) A. L. Coughlin, D. Xie, Y. Yao, X. Zhan, Q. Chen, H. Hewa-Walpitage, X. Zhang, H. Guo, H. Zhou, J. Lou, J. Wang, Y. S. Li, H. A. Fertig and S. Zhang, *ACS Nano*, 2020, **14**, 15256–15266, DOI: 10.1021/acsnano.0c05534.
- (121) R. Saha, H. L. Meyerheim, B. Göbel, B. K. Hazra, H. Deniz, K. Mohseni, V. Antonov, A. Ernst, D. Knyazev, A. Bedoya-Pinto, I. Mertig and S. S. Parkin, *Nature Communications*, 2022, **13**, DOI: 10.1038/s41467-022-31319-y.



- (122) B. Li, X. Deng, W. Shu, X. Cheng, Q. Qian, Z. Wan, B. Zhao, X. Shen, R. Wu, S. Shi, H. Zhang, Z. Zhang, X. Yang, J. Zhang, M. Zhong, Q. Xia, J. Li, Y. Liu, L. Liao, Y. Ye, L. Dai, Y. Peng, B. Li and X. Duan, *Materials Today*, 2022, **57**, 66–74, DOI: 10.1016/j.mattod.2022.04.011.
- (123) X. H. Luo, W. J. Ren and Z. D. Zhang, *Journal of Magnetism and Magnetic Materials*, 2018, **445**, 37–43, DOI: 10.1016/j.jmmm.2017.08.078.
- (124) M. Huang, S. Wang, Z. Wang, P. Liu, J. Xiang, C. Feng, X. Wang, Z. Zhang, Z. Wen, H. Xu, G. Yu, Y. Lu, W. Zhao, S. A. Yang, D. Hou and B. Xiang, *ACS Nano*, 2021, **15**, 9759–9763, DOI: 10.1021/acsnano.1c00488.
- (125) B. Tang, X. Wang, M. Han, X. Xu, Z. Zhang, C. Zhu, X. Cao, Y. Yang, Q. Fu, J. Yang, X. Li, W. Gao, J. Zhou, J. Lin and Z. Liu, *Nature Electronics*, 2022, **5**, 224–232, DOI: 10.1038/s41928-022-00754-6.
- (126) L. Z. Zhang, X. D. He, A. L. Zhang, Q. L. Xiao, W. L. Lu, F. Chen, Z. Feng, S. Cao, J. Zhang and J. Y. Ge, *APL Materials*, 2020, **8**, DOI: 10.1063/1.5143387.
- (127) A. F. Andresen, E. Zeppezauer, T. Boive, B. Nordström and C. Brändén, *Acta Chemica Scandinavica*, 1970, **24**, 3495–3509, DOI: 10.3891/acta.chem.scand.24-3495.
- (128) J. Dijkstra, H. H. Weitering, C. F. van Bruggen, C. Haas and R. A. de Groot, *Journal of Physics: Condensed Matter*, 1989, **1**, 9141–9161, DOI: 10.1088/0953-8984/1/46/008.
- (129) K. Lukoschus, S. Kraschinski, C. Näther, W. Bensch and R. K. Kremer, *Journal of Solid State Chemistry*, 2004, **177**, 951–959, DOI: 10.1016/j.jssc.2003.09.041.
- (130) T. Hamasaki, T. Hashimoto, Y. Yamaguchi and H. Watanabe, *Solid State Communications*, 1975, **16**, 895–897, DOI: 10.1016/0038-1098(75)90888-1.
- (131) S. Polesya, S. Mankovsky, D. Benea, H. Ebert and W. Bensch, *Journal of Physics Condensed Matter*, 2010, **22**, DOI: 10.1088/0953-8984/22/15/156002.
- (132) H. Y. Lv, W. J. Lu, D. F. Shao, Y. Liu and Y. P. Sun, *Physical Review B - Condensed Matter and Materials Physics*, 2015, **92**, DOI: 10.1103/PhysRevB.92.214419.
- (133) J. Zhong, M. Wang, T. Liu, Y. Zhao, X. Xu, S. Zhou, J. Han, L. Gan and T. Zhai, *Nano Research*, 2022, **15**, 1254–1259, DOI: 10.1007/s12274-021-3633-3.
- (134) L. S. Xie, S. Husremović, O. Gonzalez, I. M. Craig and D. K. Bediako, *Journal of the American Chemical Society*, 2022, **144**, 9525–9542, DOI: 10.1021/jacs.1c12975.
- (135) X. Zhao, P. Song, C. Wang, A. C. Riis-Jensen, W. Fu, Y. Deng, D. Wan, L. Kang, S. Ning, J. Dan, T. Venkatesan, Z. Liu, W. Zhou, K. S. Thygesen, X. Luo, S. J. Pennycook and K. P. Loh, *Nature*, 2020, **581**, 171–177, DOI: 10.1038/s41586-020-2241-9.
- (136) D. R. Klein, D. Macneill, J. L. Lado, D. Soriano, E. Navarro-Moratalla, K. Watanabe, T. Taniguchi, S. Manni, P. Canfield, J. Fernández-Rossier and P. Jarillo-Herrero, *Science*, 2018, **360**, 1218–1222, DOI: 10.1126/science.
- (137) Y. Liu, L. Wu, X. Tong, J. Li, J. Tao, Y. Zhu and C. Petrovic, *Scientific Reports*, 2019, **9**, DOI: 10.1038/s41598-019-50000-x.
- (138) N. Ubrig, Z. Wang, J. Teyssier, T. Taniguchi, K. Watanabe, E. Giannini, A. F. Morpurgo and M. Gibertini, *2D Materials*, 2020, **7**, DOI: 10.1088/2053-1583/ab4c64.
- (139) D. A. Wahab, M. Augustin, S. M. Valero, W. Kuang, S. Jenkins, E. Coronado, I. V. Grigorieva, I. J. Vera-Marun, E. Navarro-Moratalla, R. F. Evans, K. S. Novoselov and E. J. Santos, *Advanced Materials*, 2021, **33**, 2004138, DOI: 10.1002/adma.202004138.
- (140) Y. Feng, X. Wu, L. Hu and G. Gao, *Journal of Materials Chemistry C*, 2020, **8**, 14353–14359, DOI: 10.1039/d0tc04156d.
- (141) C. Xu, C. Carnahan, H. Zhang, M. Sretenovic, P. Zhang, D. Xiao and X. Ke, *Physical Review B*, 2023, **107**, DOI: 10.1103/PhysRevB.107.L060404.
- (142) Y. Guo, N. Liu, Y. Zhao, X. Jiang, S. Zhou and J. Zhao, *Chinese Physics Letters*, 2020, **37**, DOI: 10.1088/0256-307X/37/10/107506.
- (143) R. Li, J. Jiang, H. Bai and W. Mi, *Journal of Materials Chemistry C*, 2022, **10**, 14955–14962, DOI: 10.1039/d2tc03228g.
- (144) I. S. Jacobs, S. Roberts and P. E. Lawrence, *Journal of Applied Physics*, 1965, **36**, 1197–1198, DOI: 10.1063/1.1714167.
- (145) X. Zhou, B. Brzostowski, A. Durajski, M. Liu, J. Xiang, T. Jiang, Z. Wang, S. Chen, P. Li, Z. Zhong, A. Drzewiński, M. Jarosik, R. Szcześniak, T. Lai, D. Guo and D. Zhong, *Journal of Physical Chemistry C*, 2020, **124**, 9416–9423, DOI: 10.1021/acs.jpcc.0c03050.
- (146) E. Maniv, R. A. Murphy, S. C. Haley, S. Doyle, C. John, A. Maniv, S. K. Ramakrishna, Y. L. Tang, P. Ercius, R. Ramesh, A. P. Reyes, J. R. Long and J. G. Analytis, *Nature Physics*, 2021, **17**, 525–530, DOI: 10.1038/s41567-020-01123-w.
- (147) J. G. Checkelsky, M. Lee, E. Morosan, R. J. Cava and N. P. Ong, *Physical Review B*, 2008, **77**, 014433, DOI: 10.1103/PhysRevB.77.014433.
- (148) N. L. Nair, E. Maniv, C. John, S. Doyle, J. Orenstein and J. G. Analytis, *Nature Materials*, 2020, **19**, 153–157, DOI: 10.1038/s41563-019-0518-x.
- (149) K. T. Ko, K. Kim, S. B. Kim, H. D. Kim, J. Y. Kim, B. I. Min, J. H. Park, F. H. Chang, H. J. Lin, A. Tanaka and S. W. Cheong, *Physical Review Letters*, 2011, **107**, DOI: 10.1103/PhysRevLett.107.247201.
- (150) Y. Togawa, Y. Kousaka, K. Inoue and J. I. Kishine, *Journal of the Physical Society of Japan*, 2016, **85**, 112001, DOI: 10.7566/JPSJ.85.112001.



- (151) N. J. Ghimire, M. A. McGuire, D. S. Parker, B. Sipos, S. Tang, J. -Y. Yan, B. C. Sales and D. Mandrus, *Physical Review B*, 2013, **87**, 104403, DOI: 10.1103/PhysRevB.87.104403.
- (152) N. Sirica, P. Vilmercati, F. Bondino, I. Pis, S. Nappini, S. K. Mo, A. V. Fedorov, P. K. Das, I. Vobornik, J. Fujii, L. Li, D. Sapkota, D. S. Parker, D. G. Mandrus and N. Mannezza, *Communications Physics*, 2020, **3**, DOI: 10.1038/s42005-020-0333-3.
- (153) E. Maniv, N. L. Nair, S. C. Haley, S. Doyle, C. John, S. Cabrini, A. Maniv, S. K. Ramakrishna, Y.-L. Tang, P. Ercius, R. Ramesh, Y. Tserkovnyak, A. P. Reyes and J. G. Analytis, *Scientific Advances*, 2021, **7**, DOI: 10.1126/sciadv.abd8452.
- (154) A. Little, C. Lee, C. John, S. Doyle, E. Maniv, N. L. Nair, W. Chen, D. Rees, J. W. Venderbos, R. M. Fernandes, J. G. Analytis and J. Orenstein, *Nature Materials*, 2020, **19**, 1062–1067, DOI: 10.1038/s41563-020-0681-0.
- (155) W. J. Hardy, C. W. Chen, A. Marcinkova, H. Ji, J. Sinova, D. Natelson and E. Morosan, *Physical Review B - Condensed Matter and Materials Physics*, 2015, **91**, DOI: 10.1103/PhysRevB.91.054426.
- (156) M. Eibschütz, S. Mahajan, F. J. Disalvo, G. W. Hull and J. V. Waszczak, *Journal of Applied Physics*, 1981, **52**, 2098–2100, DOI: 10.1063/1.329629.
- (157) M. Koyano, H. Watanabe, Y. Yamamura, T. Tsuji and S. Katayama, *Molecular Crystals and Liquid Crystals Science and Technology Section A: Molecular Crystals and Liquid Crystals*, 2000, **341**, 33–38, DOI: 10.1080/10587250008026113.
- (158) T. Tsuji, Y. Yamamura, M. Koyano, S. Katayama and M. Ito, *Journal of Alloys and Compounds*, 2001, **317**, 213–216, DOI: 10.1016/S0925-8388(00)01329-3.
- (159) T. Moriya and T. Miyadai, *Solid State Communications*, 1982, **42**, 209–212, DOI: 10.1016/0038-1098(82)91006-7.
- (160) K. Du, F.-T. Huang, J. Kim, S. J. Lim, K. Gamage, J. Yang, M. Mostovoy, J. Garlow, M.-G. Han, Y. Zhu and S.-W. Cheong, *Proceedings of the National Academy of Sciences*, 2021, **118**, DOI: 10.1073/pnas.2023337118/-/DCSupplemental.
- (161) D. Obeysekera, K. Gamage, Y. Gao, S. w. Cheong and J. Yang, *Advanced Electronic Materials*, 2021, **7**, DOI: 10.1002/aelm.202100424.
- (162) Y. Togawa, T. Koyama, K. Takayanagi, S. Mori, Y. Kousaka, J. Akimitsu, S. Nishihara, K. Inoue, A. S. Ovchinnikov and J. Kishine, *Physical Review Letters*, 2012, **108**, DOI: 10.1103/PhysRevLett.108.107202.
- (163) C. Zhang, Y. Yuan, M. Wang, P. Li, J. Zhang, Y. Wen, S. Zhou and X. X. Zhang, *Physical Review Materials*, 2019, **3**, DOI: 10.1103/PhysRevMaterials.3.114403.
- (164) J. M. Pereira, D. Tezze, M. Ormaza, L. E. Hueso and M. Gobbi, *Advanced Physics Research*, 2023, **2**, DOI: 10.1002/apxr.202200084.
- (165) M. Mi, X. Zheng, S. Wang, Y. Zhou, L. Yu, H. Xiao, H. Song, B. Shen, F. Li, L. Bai, Y. Chen, S. Wang, X. Liu and Y. Wang, *Advanced Functional Materials*, 2022, **32**, DOI: 10.1002/adfm.202112750.
- (166) S. Samanta, H. Iturriaga, T. T. Mai, A. J. Biacchi, R. Islam, A. R. Hight Walker, M. F. Sanad, C. Phatak, R. Siebenaller, E. Rowe, M. A. Susner, F. Xue and S. R. Singamaneni, *arXiv*, 2023, DOI: 10.48550/arXiv.2312.01270.
- (167) R. Clément, J. J. Girerd, I. Morgenstern-Badarau, J. Rouxel, B. E. Taylor, J. Steger, A. Wold and J. Solid, *Inorganic Chemistry*, 1980, **19**, 2852–2854, DOI: 10.1021/ic50211a079.
- (168) S. Bénard, A. Léaustic, E. Rivière, R. Yu and P. Clément, *Chemistry of Materials*, 2001, **13**, 3709–3716, DOI: 10.1021/cm011019j.
- (169) X. Ma, L. Zhang, C. Xu, Q. Dong, R. I. Walton, Z. Li, Shi Honglong, Chen Genfu, Hu Jiangping and Yang Huaxin, *Chemical Communications*, 2022, **56**, 4603–4606, DOI: 10.1039/DOCC00636J.
- (170) P. Fuentealba, V. Paredes-Garcia, D. Venegas-Yazigi, I. D. Silva, C. J. Magon, R. Costa De Santana, N. Audebrand, J. Manzur and E. Spodine, *RSC Advances*, 2017, **7**, 33305–33313, DOI: 10.1039/c7ra05089e.
- (171) G. Abellán, J. L. Jordá, P. Atienzar, M. Varela, M. Jaafar, J. Gómez-Herrero, F. Zamora, A. Ribera, H. García and E. Coronado, *Chemical Science*, 2015, **6**, 1949–1958, DOI: 10.1039/c4sc03460k.
- (172) A. Léaustic, J. P. Audié, D. Cointereau, R. Clément, L. Lomas, F. Varret and H. Constant-Machado, *Chemistry of Materials*, 1996, **8**, 1954–1961, DOI: 10.1021/cm960059y.
- (173) Z. Li, X. Zhang, X. Zhao, J. Li, T. S. Herng, H. Xu, F. Lin, P. Lyu, X. Peng, W. Yu, X. Hai, C. Chen, H. Yang, J. Martin, J. Lu, X. Luo, A. H. Castro Neto, S. J. Pennycook, J. Ding, Y. Feng and J. Lu, *Advanced Materials*, 2020, **32**, DOI: 10.1002/adma.201907645.
- (174) G. T. Lin, H. L. Zhuang, X. Luo, B. J. Liu, F. C. Chen, J. Yan, Y. Sun, J. Zhou, W. J. Lu, P. Tong, Z. G. Sheng, Z. Qu, W. H. Song, X. B. Zhu and Y. P. Sun, *Physical Review B*, 2017, **95**, DOI: 10.1103/PhysRevB.95.245212.
- (175) Y. Sun, R. C. Xiao, G. T. Lin, R. R. Zhang, L. S. Ling, Z. W. Ma, X. Luo, W. J. Lu, Y. P. Sun and Z. G. Sheng, *Applied Physics Letters*, 2018, **112**, DOI: 10.1063/1.5016568.
- (176) A. Milosavljević, A. Šolajić, S. Djurdjić-Mijin, J. Pešić, B. Višić, Y. Liu, C. Petrovic, N. Lazarević and Z. V. Popović, *Physical Review B*, 2019, **99**, DOI: 10.1103/PhysRevB.99.214304.
- (177) Y. Liu, J. Li, J. Tao, Y. Zhu and C. Petrovic, *Scientific Reports*, 2019, **9**, DOI: 10.1038/s41598-019-49654-4.



- (178) M. E. Kamminga, S. J. Cassidy, P. P. Jana, M. Elgaml, N. D. Kelly and S. J. Clarke, *Dalton Transactions*, 2021, **50**, 11376–11379, DOI: 10.1039/d1dt00960e.
- (179) Q. Qian, H. Ren, J. Zhou, Z. Wan, J. Zhou, X. Yan, J. Cai, P. Wang, B. Li, Z. Sofer, B. Li, X. Duan, X. Pan, Y. Huang and X. Duan, *Nature*, 2022, **606**, 902–908, DOI: 10.1038/s41586-022-04846-3.
- (180) M. S. Whittingham, *Progress in Solid State Chemistry*, 1978, **12**, 41–99, DOI: 10.1016/0079-6786(78)90003-1.
- (181) T. Yajima, M. Koshiko, Y. Zhang, T. Oguchi, W. Yu, D. Kato, Y. Kobayashi, Y. Orikasa, T. Yamamoto, Y. Uchi-moto, M. A. Green and H. Kageyama, *Nature Communi-cations*, 2016, **7**, DOI: 10.1038/ncomms13809.
- (182) V. F. Sears, *Neutron News*, 1992, **3**, 26–37, DOI: 10.1080/10448639208218770.
- (183) A. Rauch and W. Waschkowski, in *Neutron Data Booklet*, Old City, 2nd, 2003.
- (184) R. Yang, Y. Fan, L. Mei, H. S. Shin, D. Voiry, Q. Lu, J. Li and Z. Zeng, *Nature Synthesis*, 2023, **2**, 101–118, DOI: 10.1038/s44160-022-00232-z.
- (185) M. Wang and K. J. Koski, *Journal of Physics Condensed Matter*, 2016, **28**, DOI: 10.1088/0953-8984/28/49/494002.
- (186) Y. R. Li, A. S. Poyraz, X. Hu, M. Cui, C. R. Clayton, L. Wu, Y. Zhu, E. S. Takeuchi, A. C. Marschlok and K. J. Takeuchi, *Journal of The Electrochemical Society*, 2017, **164**, A2151–A2158, DOI: 10.1149/2.1431709jes.
- (187) A. D. Hillier, D. M. Paul and K. Ishida, *Microchemical Jour-nal*, 2016, **125**, 203–207, DOI: 10.1016/j.microc.2015.11.031.
- (188) A. D. Hillier, S. J. Blundell, I. McKenzie, I. Umegaki, L. Shu, J. A. Wright, T. Prokscha, F. Bert, K. Shimomura, A. Berlie, H. Alberto and I. Watanabe, *Nature Reviews Meth-ods Primers*, 2022, **2**, DOI: 10.1038/s43586-021-00089-0.
- (189) S. De Graaf, J. Momand, C. Mitterbauer, S. Lazar and B. J. Kooi, *Science Advances*, 2020, **6**, DOI: 10.1126/sciadv.aay4312.
- (190) M. Azhagurajan, T. Kajita, T. Itoh, Y. G. Kim and K. Itaya, *Journal of the American Chemical Society*, 2016, **138**, 3355–3361, DOI: 10.1021/jacs.5b11849.
- (191) F. Li, J. Zou, L. Cao, Z. Li, S. Gu, Y. Liu, J. Zhang, H. Liu and Z. Lu, *Journal of Physical Chemistry C*, 2019, **123**, 5067–5072, DOI: 10.1021/acs.jpcc.8b09898.
- (192) K. F. Mak, J. Shan and D. C. Ralph, *Nature Reviews Physics*, 2019, **1**, 646–661, DOI: 10.1038/s42254-019-0110-y.
- (193) B. Zhou, Y. Wang, G. B. Osterhoudt, P. Lampen-Kelley, D. Mandrus, R. He, K. S. Burch and E. A. Henriksen, *Journal of Physics and Chemistry of Solids*, 2019, **128**, 291–295, DOI: 10.1016/j.jpcs.2018.01.026.
- (194) A. J. Browne, A. Krajewska and A. S. Gibbs, *Journal of Materials Chemistry C*, 2021, **9**, 11640–11654, DOI: 10.1039/d1tc02070f.
- (195) H. Zabel and S. M. Shapiro, *Physical Review B*, 1987, **36**, 7292, DOI: 10.1103/PhysRevB.36.7292.
- (196) K. Sugihara, K. Kobayashi and H. Oshima, *Journal of the Physical Society of Japan*, 1990, **59**, 2865–2874, DOI: 10.1143/JPSJ.59.2865.
- (197) D. G. Wiesler, H. Zabel and S. M. Shapiro, *Zeitschrift für Physik B*, 1994, **93**, 277–297, DOI: 10.1007/BF01312698.
- (198) J. N. Coleman, M. Lotya, A. O’neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, I. V. Shvets, S. K. Arora, G. Stanton, H.-Y. Kim, K. Lee, G. T. Kim, G. S. Duesberg, T. Hallam, J. J. Boland, J. J. Wang, J. F. Donegan, J. C. Grunlan, G. Moriarty, A. Shme-liov, R. J. Nicholls, J. M. Perkins, E. M. Grievson, K. Theuwissen, D. W. McComb, P. D. Nellist and V. Nicolosi, *Science*, 2011, **331**, 568–571, DOI: 10.1126/science.1194975.
- (199) Z. Lin, Y. Liu, U. Halim, M. Ding, Y. Liu, Y. Wang, C. Jia, P. Chen, X. Duan, C. Wang, F. Song, M. Li, C. Wan, Y. Huang and X. Duan, *Nature*, 2018, **562**, 254–258, DOI: 10.1038/s41586-018-0574-4.



No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

[View Article Online](#)
DOI: 10.1039/D4MA00539B

Open Access Article. Published on 22/07/2024. Downloaded on 24/07/2024 5:20:29.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

