



Cite this: *Green Chem.*, 2024, **26**, 2623

## Upgrading AquaSolv Omni (AqSO) biorefinery: access to highly ethoxylated lignins in high yields through reactive extraction (REx)<sup>†‡</sup>

Davide Rigo,<sup>id</sup>\*<sup>a</sup> Nadine Kohlhuber,<sup>id</sup><sup>b</sup> Lukas Fliri,<sup>id</sup><sup>a</sup> Daryna Diment,<sup>a</sup> Mijung Cho,<sup>a</sup> Ivan Sumerskii,<sup>c</sup> Michael Hummel,<sup>id</sup><sup>a</sup> Antje Potthast<sup>id</sup><sup>b</sup> and Mikhail Balakshin<sup>§</sup><sup>a</sup>

Chemical modification of lignin (*i.e.*, ethoxylation) improves its properties for specific applications. Reactive extraction (REx)—the simultaneous functionalization and extraction of lignin from biomass—is a green, simple, and powerful solution to minimize subsequent steps in biorefinery operations, while upgrading the isolated products (*i.e.*, lignin or lignin-carbohydrate hybrids). In this work, we successfully introduced REX into our recently reported AquaSolv Omni (AqSO) integrated biorefinery. Here, hydrothermally treated wood solids were refluxed with various EtOH : H<sub>2</sub>O mixtures (70–99 v/v%) in the presence of catalytic amounts of H<sub>2</sub>SO<sub>4</sub> (*c* = 0.15–1.2 M). The effects of the process variables on the structures and properties of the obtained lignins and residual solids were elucidated by comprehensive NMR analyses (HSQC, quantitative <sup>13</sup>C and <sup>31</sup>P), differential scanning calorimetry (DSC), and gel permeation chromatography (GPC). In addition, we discuss different analytical approaches—NMR vs. chromatographic methods for the quantification of ethoxy groups in lignin. Implementing REX allowed the isolation of ethoxylated lignins in 27–52% yields (based on the initial lignin content) and to tune the degree of substitution (DS) up to 40.8 EtO-groups/100 Ar (based on quantitative <sup>13</sup>C NMR)—which is approximately five times higher compared to other established organosolv processes (*i.e.*, Alcell). Moreover, solution state NMR analysis of residual solids after REX showed that ethoxylation also occurs in the cellulose-rich fraction. REX highly ethoxylated lignins produced through a simple and green process enhanced the performance of polyurethane (PU) adhesive formulations compared to formulations using non-ethoxylated lignins.

Received 6th October 2023,  
Accepted 4th January 2024

DOI: 10.1039/d3gc03776b

rsc.li/greenchem

## Introduction

Lignin as one of the main constituents of lignocellulosic biomass is the most abundant aromatic biopolymer in nature. Consequently, lignin is considered as one of the most promising sustainable and renewable feedstocks for the substitution of aromatic fuels and materials.<sup>1</sup> Today, Kraft pulping is the most common industrial process, in which the isolation of Kraft lignin (KL) is technically limited to 5–15%,<sup>2</sup> which corres-

ponds only to about 1–5% of the original biomass input. The Kraft process and other well established pulping processes (*i.e.*, sulfite pulping, *etc.*) are mainly focused on the production of high-grade pulp leaving little to no space for lignin optimization (*i.e.*, tuning of the properties of the isolated technical lignin). As a consequence, the utilization of Kraft lignin in materials applications is still limited due to its complex and poorly understood structure.<sup>3</sup>

Recently, lignin-first biorefining has gained increased research interest. Such approaches follow a conceptually different strategy compared to well-established pulping processes (*e.g.*, Kraft pulping).<sup>4–6</sup> However, to unlock the full potential of biorefining, it is important to achieve value from all the biomass constituents.<sup>7</sup> In this regard, our group recently developed a parameter-controlled type of biorefinery where it is possible to tailor the product properties by adjusting the reaction conditions for custom-designed products.<sup>8,9</sup> This emerging process—called AquaSolv Omni (AqSO)—consists of a parameter controlled hydrothermal treatment (HTT) of birch wood based on process severity (*P*-factor) followed by solvent extraction of the resulting solids at ambient tempera-

<sup>a</sup>Department of Bioproducts and Biosystems, Aalto University, Vuorimiehentie 1, Espoo, 02150, Finland. E-mail: [davide.rigo@unive.it](mailto:davide.rigo@unive.it)

<sup>b</sup>Department of Chemistry, Institute of Chemistry of Renewable Resources, University of Natural Resources and Life Sciences, Vienna (BOKU), Konrad-Lorenz-Strasse 24, 3430 Tulln an der Donau, Austria

<sup>c</sup>Core Facility of Analysis of Lignocellulosics (ALICE), University of Natural Resources and Life Sciences, Vienna, Konrad-Lorenz-Strasse 24, 3430 Tulln an der Donau, Austria

<sup>†</sup>In memory of Prof. of Practice Mikhail Balakshin.

<sup>‡</sup>Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3gc03776b>

<sup>§</sup>Deceased, 2022.



ture. AqSO can be easily coupled with other biorefinery streamlines and allows a straightforward and environmentally friendly tuning of lignin characteristics.

Certain lignin modifications (*i.e.* alkylation, acylation, ethoxylation, *etc.*) are able to upgrade lignin towards particular applications, such as thermoplastic blends, carbon fibers, surfactants, and sorbents.<sup>10–15</sup> For example, acetylation of Softwood Kraft lignin enabled dry spinning of its concentrated solutions in acetone (75 wt%).<sup>14</sup> Full acetylation of softwood Kraft lignin prior to depolymerization was proposed as a strategy to debottleneck pulping mills.<sup>16</sup> A combined acetylation and poly-esterification of Kraft lignin allowed the synthesis of fully renewable thermosets with tunable mechanical properties.<sup>17</sup> Furthermore, it has been reported that the ethoxylation of lignin increases the hydrophobicity, thermal mobility, and spinnability of lignin.<sup>18–22</sup>

When lignin modification is performed, usually a degree of substitution (DS) of 100% is targeted, *i.e.*, all available hydroxyl groups are converted into their corresponding acetylated or alkylated derivatives. However, quantitative lignin modifications typically require expensive and/or toxic chemicals (*i.e.*, dichloroethane,<sup>23</sup> 1,6-dibromohexane<sup>24</sup> and dimethyl sulfate (DMS)<sup>25</sup>) and, therefore, are often not feasible on an industrial scale. However, most applications may not require complete substitution. For instance, Sumerskii *et al.* reported that partially methylated lignins performed better in polyurethane (PU) adhesive formulations than fully methylated lignins.<sup>23</sup>

Reactive extraction (REx) allows for the simultaneous functionalization and extraction of lignin from biorefinery residues and represents an inexpensive, straightforward, and scalable method to obtain partially derivatized lignins. In a

recently patented approach,<sup>26</sup> lignin was extracted under solvent reflux with either aqueous ethanol (or other alcohols, such as methanol and propanol) or acetic acid (or other small organic acids) in the presence of catalytic amounts of a strong acid (*i.e.*, H<sub>2</sub>SO<sub>4</sub>). This approach allowed the incorporation of up to 23% ethyl or acetyl groups per 100 Ar.<sup>26</sup> Lawoko *et al.* reported a similar but more laborious procedure—where the hydrothermal treatment of wood was combined with a cyclic organosolv extraction.<sup>4,27</sup> Other research groups focused on simultaneous lignin extraction and functionalization by avoiding recombination reactions between lignin units<sup>28,29</sup> or mild organosolv extractions.<sup>30</sup> Despite the recent efforts of various research groups, the development of the REX concept is still far from being optimized. In particular, a thorough investigation of the effects of different process variables together with a comprehensive lignin characterization is still missing in the literature.

We herein demonstrate the possibility of integrating REX within our developed AqSO biorefinery,<sup>8</sup> which allows us to simultaneously upgrade/functionalize and extract lignins with tunable functionalities and properties. Throughout this study the effects of multiple variables (time, solvent-reagent concentration, and catalyst amount) on the yields, chemical structure and composition of the major products have been elucidated, with particular focus on the degree of substitution (DS) with ethoxy groups in lignin. The extracted lignins were comprehensively characterized by wet chemistry methods, NMR (HSQC, <sup>13</sup>C and <sup>31</sup>P), differential scanning calorimetry (DSC), and gel permeation chromatography (GPC). The major strengths of REX will be discussed. An outlook for the REX integrated biorefinery is depicted in Fig. 1. There are two major products of

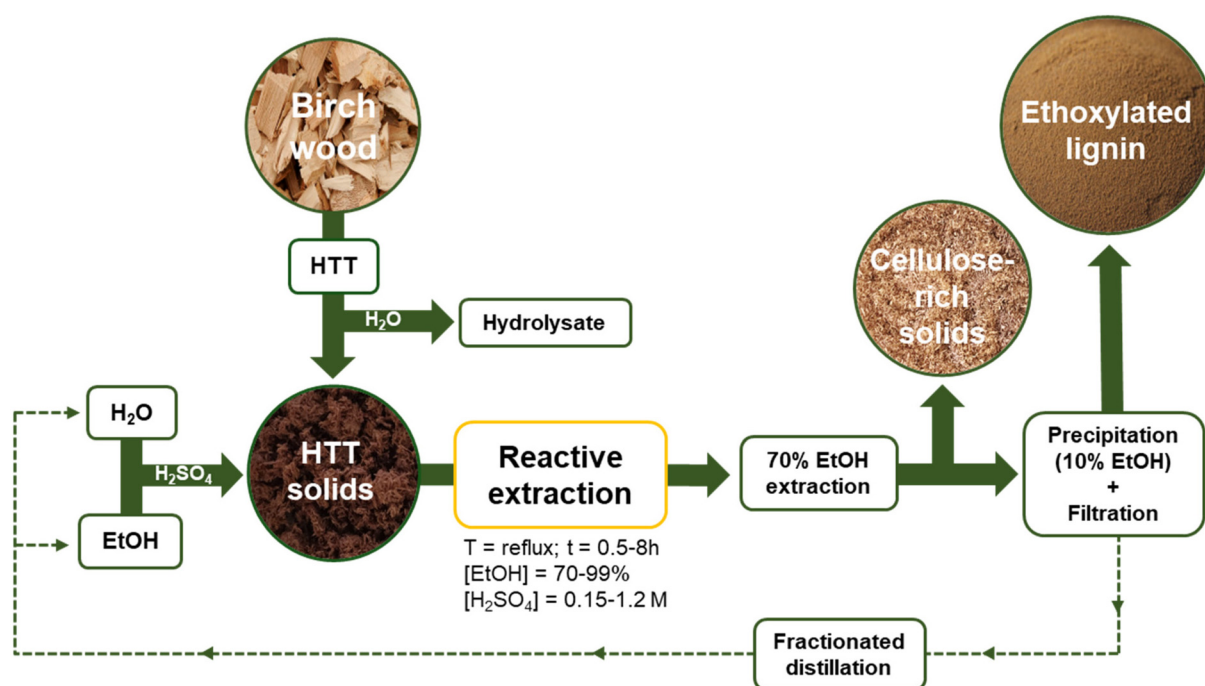


Fig. 1 Schematic representation of reactive extraction (REx).



REx: (i) reactive extracted (ethoxylated) lignin (REL) and (ii) residual (ethoxylated) solids (RS).

## Experimental

### General

Silver birch (*Betula Pendula*) wood chips were supplied by VTT (Espoo, Finland). Wood material was ground into sawdust using a Wiley mill M02 with a screen size of less than 0.5 mm and further screened with a Retsch AS 300 Control Vibratory Sieve Shaker – RAMI (0.55–0.15 mm particle size). EtOH, H<sub>2</sub>SO<sub>4</sub>, HI, methyl iodide, ethyl iodide, propyl iodide, DMSO-*d*<sub>6</sub>, CDCl<sub>3</sub>, pyridine, and 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane were purchased from Sigma Aldrich (Merck) and used without any further purification. The tetra-*n*-butylphosphonium acetate [P<sub>4444</sub>][OAc] – DMSO-*d*<sub>6</sub> direct dissolution electrolyte for solution state NMR investigations of the cellulosic fractions was either prepared according to published procedures<sup>31</sup> or sourced from Innotope. The solvent free polymeric diphenylmethane diisocyanate (pMDI) with an average functionality of 2.7 and an NCO content of 30–32 wt% was obtained from BorsodChem Zrt. (Kazincbarcika, Hungary).

### Hydrothermal treatment (HTT) of birch wood

Prior to reactive extraction, hydrothermal treatment of birch wood was performed by adjusting our previously reported procedure.<sup>8</sup> In brief, birch wood sawdust (31.6 g with 4.9% moisture content corresponding to 30.0 g o.d. wood) was placed inside a stainless-steel autoclave together with the required amount of water (28.5 g) to reach a liquid-to-solid ratio (L/S) of 1. The reactor was then closed and the mixture was allowed to react until the desired process severity (*P*-factor) of 500 was reached (*T* = 180 °C). More details about the *P*-factor calculation are reported in our previous works.<sup>8,9</sup> Once the reaction was complete, the reactor was cooled down fast (from 180 °C to *T* < 100 °C within 2 min) and the treated solids were exhaustively washed with deionized water. The hydrothermally treated solids (*P*-factor = 500) were labelled as S-500.

### Reactive extraction (REx)

REx was performed under different conditions with the apparatus depicted in the ESI (Table S1 and Fig. S1†). In a typical experiment, a round bottom flask was filled with S-500 (4 g dry matter), EtOH:H<sub>2</sub>O mixtures (70–99%; 50 mL), and variable amounts of H<sub>2</sub>SO<sub>4</sub> as the catalyst (*c* = 0.15–1.2 M). Then, the mixture was set to reflux for variable time periods (0.5–8 h). Once the reaction was complete, the residual solids (RS) were filtered through a glass crucible (porosity 4) and exhaustively extracted with a 70% EtOH:H<sub>2</sub>O mixture (200 mL) to maximize the lignin yield.<sup>32</sup> Lignins were then precipitated by diluting 70% EtOH:H<sub>2</sub>O to 10% EtOH content. In the case of the control sample (refluxing S-500 with EtOH (99% aq.) for 4 h) the isolation was performed by rotary evaporation of the extracted lignin due to the lack of lignin precipitation. The

yield of reactive extracted lignins (RELS) was evaluated gravimetrically. The reactive extracted lignins were then analyzed by chromatography methods, DSC, and GPC. For selected samples additional 2D HSQC, quantitative <sup>13</sup>C and <sup>31</sup>P NMR analyses were performed (see the ESI†).

### Methoxy/ethoxy group determination by chromatography

Methoxy/ethoxy groups of the residual solid (RS) fraction and RELs were determined in duplicates according to the procedures of Goto *et al.*<sup>33</sup> and by Sumerskii *et al.*<sup>34</sup> In brief, around 1 mL of HI acid (57%) was added to a 10 mL headspace screw cap vial containing 10–15 mg of lignin and 2–5 mg of internal standards (*i.e.*, 4-(methoxy-*d*<sub>3</sub>)-benzoic acid, 4-(ethoxy-*d*<sub>5</sub>)-benzoic acid, and propyl iodide). The vials were immediately sealed with an aluminum screw cap with a PTFE covered silicone septum and heated for 3 h at 110 °C. After cooling, the samples were neutralized by injecting 4 mL of H<sub>2</sub>O through the septum. The quantification of iodomethane (CH<sub>3</sub>I) and iodoethane (C<sub>2</sub>H<sub>5</sub>I) was carried out by headspace GC-MS and GC-FID upon calibration.

## Analysis of the reactive extracted lignins (RELS)

### Nuclear magnetic resonance (NMR) spectroscopy

**HSQC NMR method.** The 2D NMR spectra were recorded with a Bruker AVANCE 600 NMR spectrometer equipped with a CryoProbe. About 80 mg of the sample were dissolved in 0.6 mL of DMSO-*d*<sub>6</sub>. The acquisition time of 77.8 ms was set for <sup>1</sup>H-dimension and 36 scans per block were performed using the 1024 collected complex points. For <sup>13</sup>C dimension, the acquisition time was 3.94 ms and 256-time increments were recorded. The 2D HSQC NMR data were manipulated with 1024 × 1024 data points applying the Qsine function for both <sup>1</sup>H and <sup>13</sup>C dimensions. The DMSO peak at δ<sub>C</sub>/δ<sub>H</sub> 39.5/2.49 ppm ppm<sup>-1</sup> was used for the calibration of the chemical shifts. The cross-peaks were assigned based on previous reports.<sup>35–39</sup> The quantity of different lignin and LCC signals was normalized using an assumption of:

$$G + S = G_2 + S_{2,6}/2 = 100 \text{ Ar}$$

This assumption implies that the condensation (substitution) at positions G<sub>2</sub> and S<sub>2,6</sub> of lignin is insignificant. However, it is still valuable for relative comparison with the literature data as this normalization is used when only HSQC spectra of lignins are available.<sup>35,40</sup> A typical HSQC spectrum is reported in the ESI.†

**<sup>31</sup>P NMR method.** The number of different hydroxyl groups was determined by <sup>31</sup>P NMR spectroscopy<sup>41</sup> in accordance with the optimized protocol using a Bruker NMR spectrometer AV III 400.<sup>42</sup> Dry lignin samples (40.00 mg) were completely dissolved in a 1.6/1 (v/v) pyridine/CDCl<sub>3</sub> solution (0.4 mL) in a 5 mL glass vial. To this mixture, an internal standard (IS) solution (100 μL) of *endo-N*-hydroxyl-5-norbornene-2,3-dicarboximide (e-HNDI) in 1.6/1 (v/v) pyridine/CDCl<sub>3</sub> (*C* = 20 mg mL<sup>-1</sup>)



was added (IS : lignin = 0.3  $\mu\text{mol mg}^{-1}$ ) together with 50  $\mu\text{L}$  of a relaxation agent ( $\text{Cr}(\text{acac})_3$ ) solution in 1.6/1 (v/v) pyridine/ $\text{CDCl}_3$  ( $C = 11.4 \text{ mg mL}^{-1}$ ). Prior to the  $^{31}\text{P}$  NMR measurement, 100  $\mu\text{L}$  of phosphitylation reagent (2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane) was added to the mixture and stirred vigorously. The acquisition time and the relaxation delay were 1 s and 5 s, respectively; 128 scans were collected. More details on how integrations and calculations were performed and the  $^{31}\text{P}$  NMR spectra are reported in the ESI.†

#### Molar mass characterization by GPC-MALLS<sub>785nm</sub>-RI in DMSO/LiBr (0.5 w/v %)

The molar mass characterization was performed in accordance with Zinovyev *et al.*<sup>43</sup> In brief, 10 mg of the dry lignin samples were dissolved in 1 mL of the eluent (DMSO/LiBr, 0.5 w/v %) and filtered through 0.45  $\mu\text{m}$  PTFE syringe prior the measurement. The following GPC setup was used for the analysis: an Ultimate 3000 autosampler and a column oven (Thermo Fisher Scientific Inc., Waltham, MA; USA); a Dionex HPLC Pump Series P580 (Dionex Softron GmbH, Germany), a Dawn Heleos II MALLS detector,  $\lambda = 785 \text{ nm}$ ; and an Optiplab T-REX differential refractive index detector,  $\lambda = 660 \text{ nm}$  (both Wyatt Technology, Santa Barbara, CA, USA). For the separation a PolarGel M guard column (7.5  $\times$  50 mm) and three PolarGel M columns (7.5  $\times$  300 mm, 5  $\mu\text{m}$  particle size) were used. The GPC system was operated under the following conditions: flow rate, 0.5  $\text{mL min}^{-1}$ ; injection volume, 10  $\mu\text{L}$ ; run time, 65 min; temperature, 35  $^\circ\text{C}$ . Data evaluation was carried out using Astra software (version 7.3.0, Wyatt Technology, Santa Barbara, CA, USA).

#### Glass transition temperatures ( $T_g$ )

The determination of glass transition temperatures was performed on a DSC 250 (TA Instruments, USA) differential scanning calorimeter (DSC). All samples were dried before the analysis for 24 h at 40  $^\circ\text{C}$  in a vacuum oven under  $\text{P}_2\text{O}_5$ . Following that, each sample (*ca.* 7 mg) was subjected to heating under a nitrogen flow (50  $\text{mL min}^{-1}$ ) at a rate of 10  $^\circ\text{C min}^{-1}$  from 25  $^\circ\text{C}$  to 150  $^\circ\text{C}$  and isothermally held for five minutes to erase the thermal history of the sample and to remove any remaining moisture. Subsequently, the samples were cooled to 25  $^\circ\text{C}$  and heated to 200  $^\circ\text{C}$  at the same rate. The  $T_g$  was determined based on the second heating curve using the TA Universal Analysis software.

## Analysis of the residual cellulosic solid fraction

#### Compositional analysis

The compositional analysis of residual solids (RS) included the quantification of acid insoluble lignin (AIL), acid soluble lignin (ASL) and carbohydrate composition using standard protocols.<sup>44</sup> A dry sample (*ca.* 0.3 g) was hydrolyzed with 3 mL of 72%  $\text{H}_2\text{SO}_4$  at 30  $^\circ\text{C}$  for 1 h. The acid solution was then diluted to 4%  $\text{H}_2\text{SO}_4$  concentration and autoclaved at 121  $^\circ\text{C}$  for 1 h. The amount of

AIL was determined gravimetrically upon filtration, while ASL was evaluated by UV spectrophotometry at 205 nm. The carbohydrate monomers released by acid hydrolysis were analyzed using a Dionex ICS 3000A ion chromatography system equipped with a CarboPac PA1 column. The compositional analysis of RS is reported in the ESI.†

#### NMR spectroscopy

**Solid state  $^{13}\text{C}$ .** Cross polarization/magic angle spinning (CP/MAS) NMR spectra were recorded on a Bruker Avance III HD 400 spectrometer with a resonance frequency of 400.13 MHz and 100.61 MHz for  $^1\text{H}$  and  $^{13}\text{C}$ , respectively, equipped with a 4 mm dual broadband CP/MAS probe. Data were acquired at a spinning rate of 12 kHz, with a CP contact time of 2 ms and SPINAL 64  $^1\text{H}$  decoupling. Chemical shifts were referenced externally against the carbonyl signal of glycine with  $d = 176.03 \text{ ppm}$ . Spectra are reported in the ESI.†

**Solution state NMR spectra.** Spectra of the cellulosic bleached and unbleached (see the ESI†) solids were obtained after dissolution in a direct dissolution electrolyte<sup>31</sup> on a Bruker NMR AV III 400 spectrometer at an acquisition temperature of 65  $^\circ\text{C}$ . The materials were characterized by quantitative  $^1\text{H}$ , diffusion-edited  $^1\text{H}$ , and multiplicity-edited  $^1\text{H}$ - $^{13}\text{C}$  HSQC experiments. The NMR samples were prepared in a [ $\text{P}_{4444}$ ][OAc]:DMSO- $d_6$  (1 : 4 wt%) electrolyte closely following the reported protocol.<sup>31</sup> In comparison to previous reports,<sup>45,46</sup> the measuring concentration had to be reduced from 5 wt% to 2.5 wt%, in order to obtain solutions with suitable viscoelastic properties. This is a consequence of the high molecular mass of the cellulosic fractions in the cellulosic solids. All samples of different solids incorporated minor insoluble fractions, presumably associated with not completely transformed wood starting material. Only after bleaching a completely soluble material was obtained. The recorded spectra are summarized in the ESI.†

## Application test of reactive extracted lignins (RELs)

#### Cohesive strength evaluation of REL/pMDI based adhesives

The evaluation of the cohesive strength of REL/pMDI adhesives was carried out according to ASTM-D799-15 using an automated bonding strength evaluation system (ABES). In brief, around 250  $\text{g m}^{-2}$  REL/pMDI adhesive was applied on a birch veneer (thickness, 0.6–0.8 mm; width, 20 mm; overlap, 5 mm) and pressed at 120  $^\circ\text{C}$  for 5 min.<sup>23,47</sup> The REL/pMDI binder consisted of 0.25 : 0.25 : 0.5 wt% parts of REL :  $\text{H}_2\text{O}$  : pMDI.

## Results and discussion

#### General

The aim of the present work was to implement REx into our AqSO biorefinery concept. Thereby, we wanted to investigate





the effects of certain variables, such as time, EtOH concentration, and catalyst ( $\text{H}_2\text{SO}_4$ ) amount on the yields, structure, and properties of the reactive extracted lignins (RELs) and the residual solids (RS), with focus on their degree of substitution (DS) with ethoxy groups.

Our previous study demonstrated that process severity ( $P$ -factor) and the liquid-to-solid (L/S) ratio are key parameters to tune the characteristics of AqSO biorefinery lignins.<sup>8</sup> Since lignin carbohydrate complexes (LCCs) are gaining attention,<sup>48</sup> in the present study we focus on the reactive extraction of LCC-rich lignins. For this reason, the  $P$ -factor was set at 500 and L/S = 1 for the preparation of the starting material, so called hydrothermal treated solids-500 (S-500), which was found to be the optimal conditions for the preparation of LCCs.<sup>8</sup> As a subsequent step, REx was carried out using different EtOH:H<sub>2</sub>O mixtures (70–99%) and variable catalytic amounts of  $\text{H}_2\text{SO}_4$  ( $c = 0.15\text{--}1.2\text{ M}$ ) for different time frames (0.5–8 h) at reflux temperature. The reaction conditions are summarized in Table S1.† RELs were then isolated through precipitation followed by filtration (Fig. 1 and experimental).

### Effects of parameters on the yields and degree of substitution (DS)

A fast and reproducible way to measure the DS with ethoxy groups in lignin is *via* chromatography.<sup>34</sup> Thus, it has been selected as the most suitable analytical protocol to investigate the effects of variables on the DS. In this part of the study the aim was two-fold: maximizing both the lignin yield and the DS with ethoxy groups.

S-500 was initially set to react with a 70% EtOH:H<sub>2</sub>O solution in the presence of a catalytic amount of  $\text{H}_2\text{SO}_4$  ( $C = 0.15\text{ M}$ ) at reflux temperature for 0.5–8 h. The real time analysis shows that the yields of RELs slightly increase until 4 h up to 48% with respect to the initial lignin content (Fig. 2b), and then remain constant for longer times. Consistently, an opposite trend was observed for the yield of residual lignin (RL), which decreases until 4 h (74 wt%; Fig. 2b) while remaining constant from this instant on. As expected, an increase of the reaction time increases the number of ethoxy groups present in RELs, reaching an equilibrium value of 11–12/100 Ar after 4 h. (Fig. 2a). Intriguingly, ethoxylation occurred in the residual solids as well, which will be discussed in more detail towards the end of the manuscript.

Based on the latter results, the reaction time was set to 4 h and the effect of the aqueous ethanol concentration was then investigated in the range of 70–99%. EtOH was found to be a crucial parameter for improving the DS of both REL and RS. The DS of REL was increased by a factor of 2.5 by increasing the EtOH concentration from 70 to 99%, where the ethoxy group content increased from 11 to 28/100 Ar, respectively (Fig. 2c). This is consistent with a competition between H<sub>2</sub>O and EtOH in favor of EtOH when its concentration was close to 99%. A similar trend was observed in RS, in which the DS increased from 17 to 32/100 Ar passing from the 70% to 99% EtOH:H<sub>2</sub>O mixture, respectively. An even higher DS of 40.8/100 Ar was obtained from quantitative <sup>13</sup>C NMR analysis,

which exceeds typical data from organosolv pulping (Table 3; entry 4) by a factor of 3.3.<sup>49</sup> Additional considerations and data correlation of different analytical techniques are discussed in the following section. Consistently, within the same EtOH concentration range (70–99%), the yields of REL and RL have opposite ~30% decreasing and increasing trends from 48% to 33% and from 31% to 45%, respectively.

To keep the REx conditions as close as possible to a simple extraction – meaning minimizing the extraction time while maximizing the DS – in 99% EtOH we set  $t = 0.5\text{ h}$  and simultaneously increased the amount of catalyst in the range  $[\text{H}_2\text{SO}_4] = 0.15\text{--}1.2\text{ M}$ . As expected, the best outcome for both yield and DS of REL was achieved with the highest  $\text{H}_2\text{SO}_4$  concentration. Within a really short time (0.5 h) we were able to isolate REL in 54% yield (with respect to the initial content), while incorporating EtO-groups up to 23/100 Ar by chromatographic quantification<sup>34</sup> (Fig. 2e) and 33.7/100 Ar by quantitative <sup>13</sup>C NMR (Table 3, entry 3). Intriguingly, under the latter conditions ( $t = 0.5\text{ h}$ ,  $[\text{EtOH}] = 99\%$ ,  $[\text{H}_2\text{SO}_4] = 1.2\text{ M}$ ) the mass balance (REL + RL) is around 97%, meaning that we were able to recover almost all lignin by precipitation/filtration (Fig. 2f). In addition, fractionated distillation of the EtOH and H<sub>2</sub>O allowed to fully recover (yield >98%) the solvent reagents in more than 99% purity (by GC), providing a proof-of-concept for the recycling/reuse of used solvents. The effects of variables on the compositional analysis of the residual solids was very subtle (see the ESI†).


### Structural characterization of reactive extracted lignins (RELs)

<sup>1</sup>H–<sup>13</sup>C heteronuclear single quantum coherence spectroscopy (HSQC) analysis revealed the most important structural changes in the lignin structure during REx (Fig. 3). Spectra of a control sample obtained from the direct extraction of S-500 with 70% aqueous ethanol and of a REL sample with the highest DS (conditions:  $t = 4\text{ h}$ ,  $[\text{EtOH}] = 99\%$ ,  $[\text{H}_2\text{SO}_4] = 0.15\text{ M}$ ,  $T = \text{reflux}$ ) are compared and discussed.

The appearance of cross peaks assigned to  $-\text{CH}_2-$  and  $\text{CH}_3-$  groups in ethoxy alkyl ethers (Table 2, entries 1 and 3) and ethoxy alkyl esters (entry 2) after REx unveils that ethoxylation of aliphatic  $-\text{OH}$  occurred together with esterification (Fig. 3). This result was further confirmed by the decrease in both aliphatic  $-\text{OH}$  and  $-\text{COOH}$  groups obtained for the ethoxylated samples compared to blank experiments by <sup>31</sup>P NMR analysis (compare S1 and S3–4 in Table 1). Cross peaks were assigned based on the literature data<sup>50–52</sup> and Chemdraw simulations. In addition, a signal at  $\delta_{\text{H}}/\delta_{\text{C}} = 4.0\text{--}4.1/58.9\text{--}60.1$  was detected with good separation and tentatively assigned to the  $-\text{CH}_2-$  group in ethoxy aryl esters ( $\text{CH}_3\text{CH}_2\text{OCOR}$  with  $\text{R} = \text{aryl}$ ; Table 2, entry 4) based on Chemdraw simulations and the literature data.<sup>52</sup> The same signal could also be attributed to cinnamyl alcohol units as reported elsewhere.<sup>53</sup>

No evidence for ethoxylation on phenolic  $-\text{OH}$  groups (PhOH) was found, as typical cross peaks of  $-\text{CH}_2-$  and  $\text{CH}_3-$  groups in EtO-Ar units were not present in the HSQC spectra at  $\delta_{\text{H}}/\delta_{\text{C}} = 4.0\text{--}4.2/65.0\text{--}69.0$  and  $\delta_{\text{H}}/\delta_{\text{C}} = 1.3\text{--}1.4/14.0\text{--}15.0$ ,<sup>54,55</sup> respectively (Fig. S3†). The same outcome was obtained by <sup>31</sup>P



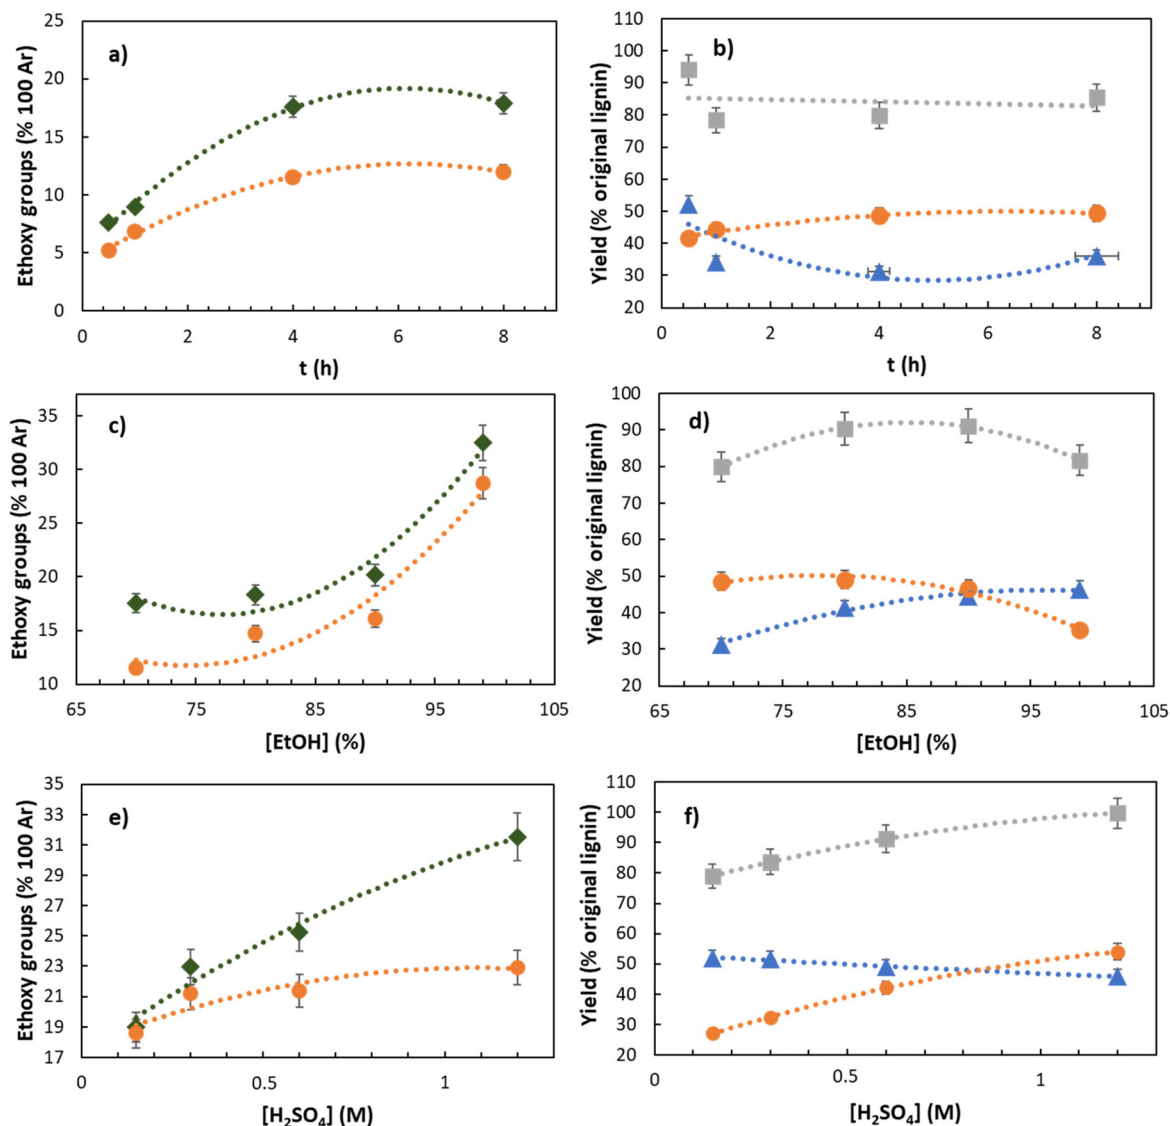


**Fig. 2** The effects of time (a and b), [EtOH] (c and d), and [H<sub>2</sub>SO<sub>4</sub>] (e and f) on the outcome of REx. at reflux. Other conditions: a and b: [H<sub>2</sub>SO<sub>4</sub>] = 0.15 M, [EtOH] = 70%; c and d: *t* = 4 h, [H<sub>2</sub>SO<sub>4</sub>] = 0.15 M; e and f: *t* = 0.5 h, [EtOH] = 99%. -●- REL = reactive extracted lignin. -◆- RS = residual solids. -▲- RL = residual lignin. -■- REL + RL. EtO-data were obtained according to wet chemistry methods.<sup>54</sup> For convenience and better comparison, data of RS are expressed per 100 Ar based on the lignin content of the solids. The yield of products is intended with respect to the lignin content in the starting material (S-500).

NMR analysis, as the amount of PhOH was constant despite changing the reaction conditions (Table 1). This is consistent with an E1 reaction mechanism, plausible under acid catalysis,<sup>56</sup> which cannot occur for PhOH.

Even though HSQC analysis provides data in a semi-quantitative way, it represents a valuable tool to relatively compare data obtained from similar lignin samples. In light of this, we quantified key lignin subunits and expressed the number per 100 Ar to provide further insights into REx (see also the Experimental section). During the course of the reaction, the number of  $\beta$ -O-4/ $\alpha$ -OH units decreased from 22.6/100 Ar before REx (Table 2, entry 1) to 10.5 and 8.7/100 Ar under the harshest conditions tested (Table 2, entries 3 and 4, respectively).

Parallely, an increase in benzyl ether (BE) units at  $\delta_{\text{H}}/\delta_{\text{C}} = 4.3\text{--}4.8/78.3\text{--}82.0$ <sup>53</sup> from 4.1/100 Ar to 23.7 and 21.3, respectively, was found, suggesting that ethoxylation occurred on the  $\alpha$ -position of  $\beta$ -O-4 bonds. More specifically, the signal at  $\delta_{\text{H}}/\delta_{\text{C}} = 4.4\text{--}4.6/78.8\text{--}80.8$  can be assigned to  $\beta$ -O-4/ $\alpha$ -OEt moieties considering the literature data<sup>53</sup> and ChemDraw simulations. In turn, a chemical shift of the signal of the CH <sub>$\alpha/\beta$</sub>  moiety in  $\beta$ -O-4/ $\alpha$ -OH units was expected. Consistently, additional cross peaks appeared at  $\delta_{\text{H}}/\delta_{\text{C}} = 4.1\text{--}4.3/83.6\text{--}85.4$  and  $3.9\text{--}4.1/83.9\text{--}85.3$  after REx which are attributed to the *erythro* and *threo* isomers of  $\beta$ -O-4/ $\alpha$ -OEt units, respectively, (structures B<sub>2</sub>-D<sub>2</sub> shown in Fig. 3) considering the literature data<sup>52</sup> and Chemdraw simulations. No proof for ethoxylation on the



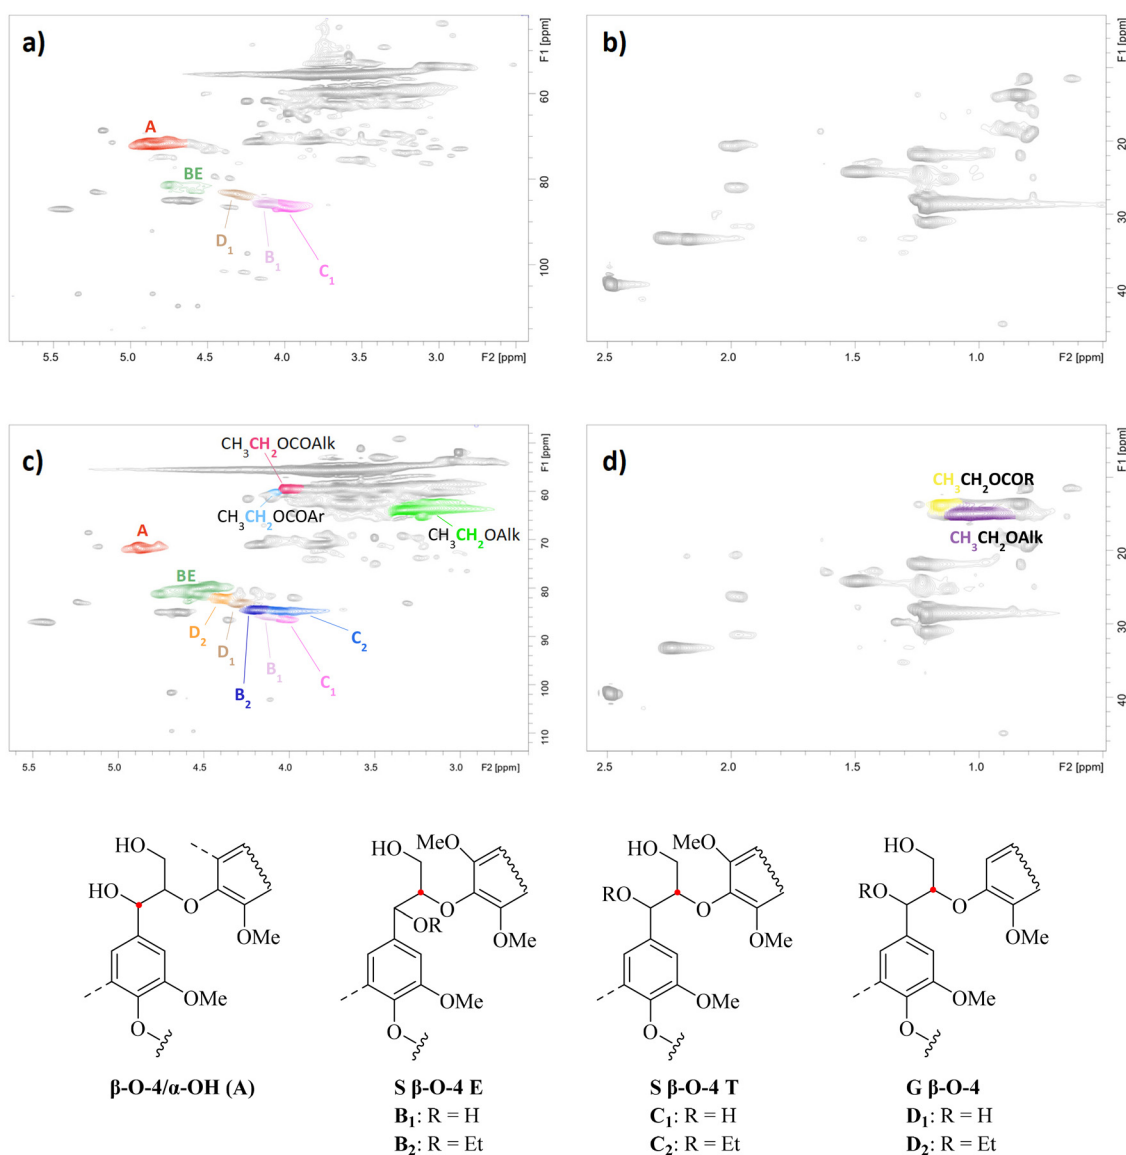

**Fig. 3** 2D HSQC spectra of ethanol extracted lignin (EEL; a and b) and reactive extracted lignin (REL; c and d). Reaction conditions to produce REL:  $t = 4$  h,  $[\text{EtOH}] = 99\%$ ,  $[\text{H}_2\text{SO}_4] = 0.15$  M,  $T = \text{reflux}$ .

**Table 1** Amount of  $-\text{OH}$  and  $-\text{COOH}$  groups in lignin samples corrected for EtO-groups and carbohydrates evaluated by  $^{31}\text{P}$  NMR

| Entry | Label           | [EtOH]<br>(%) | $t$<br>(h) | [H <sub>2</sub> SO <sub>4</sub> ]<br>(M) | -OH/-COOH (per 100 Ar) |                         |                       |                  |      |                 |              |
|-------|-----------------|---------------|------------|--|------------------------|-------------------------|-----------------------|------------------|------|-----------------|--------------|
|       |                 |               |            |  | Aliphatic              | PhOH<br>(5-substituted) | PhOH (G-type<br>n.c.) | PhOH<br>(H-type) | COOH | Total Ph-<br>OH | Total<br>-OH |
| 1     | S1              | 70            | —          | —  | 69.2                   | 45.4                    | 13.1                  | 3.0              | 7.4  | 61.5            | 130.7        |
| 2     | S2 <sup>a</sup> | 99            | 4          | —  | 63.4                   | 56.4                    | 14.5                  | 2.6              | 6.8  | 73.5            | 136.9        |
| 3     | S3              | 99            | 0.5        | 1.2                                      | 54.8                   | 44.0                    | 14.0                  | 3.0              | 3.5  | 61.0            | 115.8        |
| 4     | S4              | 99            | 4          | 0.15                                     | 48.1                   | 43.7                    | 13.6                  | 2.9              | 2.5  | 60.3            | 108.3        |

<sup>a</sup> Isolated by rotary evaporation. n.c. = non-conjugated.

$\gamma$ -position of  $\beta\text{-O-4}/\alpha\text{-OH}$  units was found due to the overlap of multiple signals at in the characteristic area at  $\delta_{\text{H}}/\delta_{\text{C}} = 3.5\text{--}4.0/70\text{--}65$ .<sup>39,57–61</sup>

As far as other lignin moieties are concerned, the effect of REX on the amount of resinol and phenylcoumaran units was insignificant, not depending on the reaction conditions (see



**Table 2** Integration range of lignin units of interest for REX

| Entry | Moiety   | Integration range ( $^1\text{H}/^{13}\text{C}$ )                         |
|-------|--|--|
| 1     | $\text{CH}_3\text{-CH}_2\text{-O-Alk}$                   | 0.8–1.1/14.0–15.9  |
| 2     | $\text{CH}_3\text{-CH}_2\text{-OCO-R}$                   | 1.1–1.2/12.9–14.6  |
| 3     | $\text{CH}_3\text{-CH}_2\text{-O-Alk}$                   | 3.0–3.4/62.1–64.9  |
| 4     | $\text{CH}_3\text{-CH}_2\text{-OCO-Alk}$                 | 3.9–4.0/58.1–60.6  |
| 5     | $\text{CH}_3\text{-CH}_2\text{-OCO-Ar}$                  | 4.0–4.1/58.9–60.1  |
| 6     | $\text{H}_\alpha$ in $\beta\text{-O-4}/\alpha\text{-OH}$ | 5.3–4.6/73.7–69.7  |
| 7     | $\text{H}_\beta$ in S $\beta\text{-O-4 E}$               | B <sub>1</sub> : 4.0–3.8/87.7–84.8<br>B <sub>2</sub> : 4.1–4.3/83.6–85.4 |
| 8     | $\text{H}_\beta$ in S $\beta\text{-O-4 T}$               | C <sub>1</sub> : 4.3–4.0/88.1–84.8<br>C <sub>2</sub> : 3.9–4.1/83.9–85.3 |
| 9     | $\text{H}_\beta$ in G $\beta\text{-O-4 (E + T)}$         | D <sub>1</sub> : 4.4–4.1/84.5–82.0<br>D <sub>2</sub> : 4.3–4.4/81.2–83.0 |

the ESI, Fig. S4 and Table S3†). The presence of lignin carbohydrate complexes (LCCs), like phenyl glycoside, benzyl ether and glucuronic ester bonds, was detected in RELs, even though in low amounts (see the ESI, Fig. S5 and Table S3†). Most likely, the majority of LCC linkages are present in the non-precipitated lignin.

### Correlation of analytical methods for the evaluation of EtO-groups

Various methods are reported in the literature for the quantitative measurement of the EtO-group content in lignin, such as wet chemistry coupled with chromatography<sup>33,34</sup> and quantitative  $^{13}\text{C}$  NMR.<sup>62</sup> Even though HSQC is only known as a semi-quantitative NMR technique, it showed in some cases good correlation with quantitative  $^{13}\text{C}$  NMR<sup>9,62</sup> and could thus be considered for the quantification of EtO-groups. However, to the best of our knowledge, no reports on the comparison of quantitative data from different techniques are present in the literature.

For this reason, we compared quantitative  $^{13}\text{C}$  and 2D HSQC NMR with conventional methods based on hydroiodic acid (HI) treatment followed by chromatography<sup>33,34</sup> and correlated the quantitative data. For HSQC, the  $-\text{CH}_2-$  and  $-\text{CH}_3$  moieties of EtOH-groups were separately considered for quantification and are presented as the number of EtO-groups/100 Ar. We analyzed samples under four different extraction conditions (Table 3):

- blank sample, extraction with 70% EtOH (S1, entry 1);
- catalyst-free REX with 99% EtOH for 4 h (S2, entry 2);
- REX with 99% EtOH and 1.2 M  $\text{H}_2\text{SO}_4$  for 0.5 h (S3, entry 3);
- REX with 99% EtOH and 0.15 M  $\text{H}_2\text{SO}_4$  for 4 h (S4, entry 4).

As expected, the blank sample after extraction with 70% aqueous EtOH showed only a negligible presence of EtO-groups (<3%) by all methods (entry 1). However, quantification by HSQC was affected by signal overlap to a certain degree, resulting in comparably higher values ( $-\text{CH}_2-$  2.9/100 Ar;  $-\text{CH}_3$  1.9/100 Ar EtO-groups; see Table 3). The results from the catalyst-free extraction (entry 2) suggest that ethoxylation may scanty occur even without a catalyst ( $t = 4$  h), since only

**Table 3** Quantification of key lignin units and comparison of different methods for the quantification of EtO-groups in RELs. All the data are expressed per 100 Ar

| Entry          | Label | [EtOH] (%) | t (h) | [ $\text{H}_2\text{SO}_4$ ] (M) | Yield (% original content) | 2D HSQC                 |      |                         |                 |                 |                 |                 |                 |                 |               | Quantitative $^{13}\text{C}$ |        |       |                        | Chromatographic |                        |
|----------------|-------|------------|-------|---------------------------------|----------------------------|-------------------------|------|-------------------------|-----------------|-----------------|-----------------|-----------------|-----------------|-----------------|---------------|------------------------------|--------|-------|------------------------|-----------------|------------------------|
|                |       |            |       |                                 |                            | Subunit                 |      | Ethers                  |                 | Alkyl esters    |                 | Aryl esters     |                 | Total           |               | Ethers                       | Esters | Total | Method 1 <sup>34</sup> |                 | Method 2 <sup>33</sup> |
|                |       |            |       |                                 |                            | $\beta\text{-O-4 a-OH}$ | BE   | BE + $\beta\text{-O-4}$ | $\text{CH}_3^a$ | $\text{CH}_2^b$ | $\text{CH}_3^a$ | $\text{CH}_2^b$ | $\text{CH}_3^a$ | $\text{CH}_2^b$ | $\text{CH}_3$ |                              |        |       |                        |                 |                        |
| 1              | S1    | 70         | —     | —                               | 28.1                       | 22.6                    | 4.1  | 26.7                    | 1.6             | 2.3             | 0.2             | 0.5             | 0.1             | 1.9             | 2.9           | —                            | —      | 0.1   | 1.4                    |                 |                        |
| 2 <sup>c</sup> | S2    | 99         | 4     | —                               | 51.9                       | 23.7                    | 4.4  | 28.1                    | 2.0             | 3.6             | 0.2             | 0.6             | 0.1             | 2.3             | 4.3           | —                            | —      | 2.0   | 2.0                    |                 |                        |
| 3              | S3    | 99         | 0.5   | 1.2                             | 54.0                       | 10.5                    | 23.7 | 34.2                    | 27.1            | 21.4            | 6.8             | 9.4             | 0.5             | 34.2            | 31.3          | 21.9                         | 11.8   | 33.7  | 22.9                   | 23.0            |                        |
| 4              | S4    | 99         | 4     | 0.15                            | 35.2                       | 8.7                     | 21.3 | 30.0                    | 33.2            | 24.6            | 6.9             | 9.7             | 0.5             | 40.5            | 34.8          | 28.5                         | 12.3   | 40.8  | 28.7                   | 24.8            |                        |

<sup>a</sup> Quantified using  $\text{CH}_3-$  moiety of EtO-group. <sup>b</sup> Quantified using  $-\text{CH}_2-$  moiety of EtO-group. <sup>c</sup> Sample obtained through rotary evaporation.





slightly higher EtO-group contents were achieved compared to the blank sample. Although sample recovery may have an influence in this particular case (see the Experimental section). RE<sub>X</sub> using H<sub>2</sub>SO<sub>4</sub> as the catalyst led to a significant increase in EtO-groups (34.2–40.5/100 Ar and 33.7–40.8/100 Ar for entries 3 and 4, respectively). Nevertheless, the presence of extractives could contribute to some extent to the EtO-group content. In this regard, dedicated work must be performed to determine the exact contribution. In addition, the decrease in vinyl structures (Fig. S4 and Table S3†) with an increase in DS suggests that incorporation of EtO-groups might occur through the addition of C=C double bonds as well.

Interestingly, 2D HSQC and <sup>13</sup>C NMR correlated well in the case of the –CH<sub>3</sub> moiety (4.4% and 0.7% deviation for entries 3 and 4, respectively). This is in line with our recent results on the correlation of HSQC and <sup>13</sup>C data for the quantification of LCCs.<sup>9</sup> The HI methods produced consistently lower values than the NMR methods, but correlated quite well with each other (entry 2, Table 3). However, the method based on HS GC-MS is regarded as more precise and accurate due to a lesser number of steps during the analysis (*i.e.*, lower risk of escape of volatile species during sample manipulation).<sup>63</sup>

In HI approaches, only ethoxy ethers (and not esters) contribute to the quantification of EtO-groups *via* the formation of methyl-/ethyl-iodide,<sup>64</sup> resulting in lower values compared to NMR approaches. Quantitative <sup>13</sup>C NMR data supports this, as the number of ethoxy ethers (not esters) are very close to the HI acid values (see Table 2). In addition, one should consider that the treatment of lignin with aqueous HI (57%) may promote hydrolysis of esters to form ethanol, which is not detected according to these methods.<sup>33,34</sup>

Overall, a good correlation between HSQC and quantitative <sup>13</sup>C was found using our pulse sequences described in the Experimental section. Moreover, evidence for the sole contribution of ethers (and not esters) in the quantification of ethoxy groups by HI-based wet chemistry methods was presented. In light of this, our suggestion is to use NMR techniques to achieve quantitative data on the total amount of EtO-groups (esters and ethers), while for a fast track of EtO-ethers, wet chemistry seems to be the most suitable methodology.

### Effects of the process variables on the molar mass distribution

GPC-MALLS<sub>785nm</sub> was used to determine the influence of the process variables (*i.e.*, reaction time, EtOH, and H<sub>2</sub>SO<sub>4</sub> concentration) on the molar mass of the obtained RELs. The MMDs and statistical moments are given in the ESI (Fig. S9 and Table S6†).

Adding H<sub>2</sub>SO<sub>4</sub> to the extracting agent (EtOH) had the greatest influence on the molar mass. Lignins extracted with EtOH and H<sub>2</sub>SO<sub>4</sub> (independent of the concentration) have higher molar masses than those extracted solely with EtOH (Fig. S9†). We propose that the increase in molar mass is mainly due to condensation reactions – known to occur during lignin extraction with EtOH under acidic conditions.<sup>65</sup> Adding H<sub>2</sub>SO<sub>4</sub> initiates acid catalysis, causing hydrolysis of benzyl ether linkages (at C<sub>α</sub>) and the formation of reactive benzyl carbo-

cations. The introduced benzyl carbocations can easily form a bond with the aromatic ring of a neighboring lignin unit.<sup>65</sup> This suggestion is further supported by the earlier reported HSQC measurements (*e.g.*, a decrease of β-O-4/α-OH).

Moreover, the applied EtOH concentration influenced the molar mass of RELs. Lignins extracted with absolute EtOH (99%) show lower dispersity in molar mass (*D<sub>M</sub>*; *i.e.*, are more homogeneous) compared to RELs extracted with aqueous EtOH (70, 80 and 90%) solutions (Fig. S9b†). We propose that the variation in the molar mass is mostly due to the difference in polarity of the used EtOH solutions. Similar effects of the EtOH concentration on the molar mass of lignins have been reported in the literature.<sup>66–69</sup> However, process parameters such as reaction time and concentration of H<sub>2</sub>SO<sub>4</sub> do not influence on the molar mass of RELs.

### Effects of process variables on the thermal properties

As the glass transition temperature (*T<sub>g</sub>*) of lignin is known to be affected by the molar mass distribution<sup>70</sup> and by plasticizing substituents,<sup>71</sup> it is expected that both the molar mass distribution and the quantity of OEt-groups would influence the *T<sub>g</sub>* of the lignin samples. As a general trend, it was found that RELs with higher molar masses contain smaller numbers of OEt-groups and *vice versa* (see MMD, Table S6 and Fig. S9†). This implies that it is hard to discriminate if the *T<sub>g</sub>* variation in RELs is ascribed to an increase in the DS and/or in the molar mass. Nevertheless, a negative linear correlation between *T<sub>g</sub>* and the DS was found (Fig. 4) which can be correlated to both a plasticizing effect of ethoxy groups and a decrease in the molar mass.

While the concentration of the catalyst (H<sub>2</sub>SO<sub>4</sub>) and the reaction time did not profoundly affect the *T<sub>g</sub>*, the concentration of EtOH played a crucial role in determining the glass transition temperature (Fig. S10†). More in detail, a sharp decrease in *T<sub>g</sub>* from 134.0 to 109.5 °C was detected by increasing the EtOH concentration from 90% to 99%, in line with the simultaneous decrease in molar mass (Fig. S9b†). In contrast, a smoother effect was found in the ethanol concentration range 70–90%. Overall, in order to produce more “thermoplastic” lignins with lower *T<sub>g</sub>* both a higher DS and lower molar mass should be targeted.

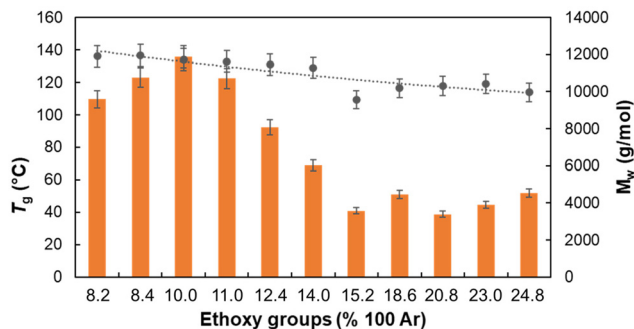


Fig. 4 The correlation between EtO-groups content, *M<sub>w</sub>* and resulting *T<sub>g</sub>* values. ●- *T<sub>g</sub>* values ■- *M<sub>w</sub>*.



### Bonding strength of REL/pMDI adhesives

The use of different lignins (*i.e.*, Kraft, lignosulfonates, organosolv, *etc.*) in adhesive formulations is one of the most promising utilization of lignin.<sup>72,73</sup> Intriguingly, Summerskii *et al.* reported recently that partially modified lignins (*i.e.* partially alkylated) have performed the best in the preparation of lignin-based PU binders.<sup>23</sup> In this context, the performance of RELs in PU adhesives for wood veneers was investigated. Therefore, REL was mixed with polymeric methylene diphenyl diisocyanate (pMDI) and tested with an Automated Bond Evaluation System (ABES). For the ABES experiments REL samples with different EtO-groups contents were selected together with two control samples (pMDI and pMDI + non-ethoxylated lignin). The obtained results are reported in Table 4.

As expected, ethoxylated lignins performed better than both the non-ethoxylated sample and the pMDI control. In addition, a clear performance improvement was found when the number of EtO-groups was increased: the highest bonding strength was measured for the sample with the highest DS (28.7 EtO-groups/100 Ar by wet chemistry; entry 4). As recently discussed,<sup>23</sup> this is consistent with higher solubility of lignin in pMDI, which is a crucial parameter to facilitate the curing process when the use of a solvent is avoided. These results provide a new opportunity for the valorization of RELs in wood adhesive formulations.

To conclude this section, a comparison of different procedures for the development of lignin-based polyurethane adhesives is given (Table 5). However, the large variations in applied lignin substrates and adhesive formulations do not allow a reliable (numerical) comparison of the adhesive performance between studies.<sup>74</sup> Consequently, the discussion will mainly focus on the differences in used additives, solvents, and catalysts as well as the advantages/disadvantages of each study.

The major advantage of the approach presented herein is the simplicity of the procedure which does not require any additives, solvents, and catalysts, while being effective in very short curing times ( $t = 5$  min, entry 1). As stated earlier, the

high degree of ethoxylation made REx lignin samples directly soluble in pMDI, facilitating the synthesis of polyurethane adhesives in a single step. The procedure by Summerskii *et al.* (entry 2) is overall similar but it is based on toxic and more expensive reagents like alkyl halides and anhydrides.<sup>23</sup> In other words, REx represents a greener and more sustainable alternative to other lignin modification procedures. Another solvent and catalyst-free procedure was reported by Tavares *et al.*<sup>75</sup> However, they needed very long curing times ( $t = 7$  days, entry 6), thus making their approach less economical. Even though in all other procedures unmodified lignin samples were used, the need for a solvent – even very toxic ones – to solubilize lignin prior to curing poses important drawbacks from a sustainability standpoint (entries 3–5). In addition, in some cases a catalyst was added (entry 3) or a pre-polymer was synthesized prior to curing (entry 5).

Overall, the procedure we proposed seems, to date, among the most attractive. The partial modification of lignin avoids the use of solvents while maintaining lignin activity. On the other hand, solvents and/or long curing times are generally requested when unmodified lignin is used. However, it should be mentioned that in our protocol a non-optimized low lignin content (25 wt%) in the formulation was used and this aspect should be improved in further studies.

### NMR analysis of the residual solids (RS)

Although the presented approach is focused on lignin, every biorefinery concept must consider full valorization of the biomass input.<sup>7</sup> Thus, the fate of the cellulose and hemicellulose constituents during REx is also important. The obtained residual solids (RS) showed the incorporation of ethoxy functionalities according to chromatography methods (Fig. 2). Consequently, we were interested in whether a chemical modification of the polysaccharide fractions occurred during the reactive extraction protocol, or if the determined ethoxy group content was associated with non-extractable modified lignin fractions or solely EtOH impurities. For this endeavor both solid state CP MAS <sup>13</sup>C NMR and solution state NMR protocol using direct dissolution of the ionic liquid electrolyte<sup>31</sup> were tentatively conducted on certain RS showing high DS values (Fig. 5). Both approaches suffered from peak superposition issues. The ethoxy CH<sub>2</sub> signal was in the same spectral range as the polysaccharide backbone. Owing to the intrinsically low resolution in the solid state <sup>13</sup>C NMR spectra leading to broad peaks, the acetyl CH<sub>3</sub> peaks of the hemicellulose content could not be sufficiently differentiated from potential ethoxy CH<sub>3</sub> moieties (Fig. S12 and S13†). In the solution state NMR spectra (Fig. S14 and S17†) significant peak superposition with the signals of [P<sub>4444</sub>][OAc] in the electrolyte was encountered. Only in the diffusion edited <sup>1</sup>H NMR experiment where signals of low molecular weight compounds are effectively suppressed in the spectra<sup>31</sup> the appearance of an additional broad peak at around 1.0–1.3 ppm (ethoxy CH<sub>3</sub>) in the residual solids (RS) clearly indicated the covalent modification of some of the polymeric fractions to a minor extent. However, as the RS proved to be partially insoluble and the

**Table 4** Adhesive performance of RELs with different EtO-group contents

| Sample            | Conditions <sup>e</sup> |         |                                       |                                    | $\sigma$ (N mm <sup>-2</sup> ) |
|-------------------|-------------------------|---------|---------------------------------------|------------------------------------|--------------------------------|
|                   | [EtOH] (%)              | $t$ (h) | [H <sub>2</sub> SO <sub>4</sub> ] (M) | EtO-groups <sup>d</sup> (% 100 Ar) |                                |
| pMDI <sup>a</sup> | —                       | —       | —                                     | —                                  | 0.6 ± 0.2                      |
| S1 <sup>b</sup>   | —                       | —       | —                                     | 1.2                                | 2.6 ± 0.5                      |
| S2 <sup>c</sup>   | 99                      | 0.5     | 0.15                                  | 18.6                               | 4.3 ± 0.8                      |
| S3 <sup>c</sup>   | 99                      | 0.5     | 1.2                                   | 23.0                               | 4.0 ± 0.1                      |
| S4 <sup>c</sup>   | 99                      | 4       | 0.15                                  | 28.7                               | 5.2 ± 0.7                      |

The REL/pMDI binder consisted of 0.25:0.25:0.5 wt% parts of REL:H<sub>2</sub>O:pMDI. <sup>a</sup> Control experiment with pMDI and without lignin. <sup>b</sup> Sample obtained from direct extraction with aqueous EtOH (70%) of lignin from S-500. <sup>c</sup> Reactive extracted lignins (RELs). <sup>d</sup> Data obtained from wet chemistry. <sup>e</sup> Conditions for the preparation of RELs.



**Table 5** Comparison of different procedures for the development of lignin-based polyurethane adhesives. Advantages and drawbacks of the overall process are pointed out

| Entry | Lignin substrate   | Formulation (wt : wt : wt) <sup>a</sup>               | Additives/solvents/catalyst  | Curing <i>T</i> and <i>t</i>        | Advantages  | Drawbacks   | Ref.                                  |
|-------|--|---|--|-------------------------------------|---|---|---------------------------------------|
| 1     | REx  | Lignin : pMDI : H <sub>2</sub> O (0.25 : 0.25 : 0.5)  | None   | <i>T</i> = 120 °C; <i>t</i> = 5 min | - Highly soluble lignins in pMDI<br>- Simple process and non-toxic reagents for lignin ethoxylation<br>- No additives<br>- Cat. Free<br>- Short curing time | - Low lignin % (non-optimized)  | This work                             |
| 2     | Modified Kraft   | Lignin : pMDI : H <sub>2</sub> O (0.33 : 0.33 : 0.33) | None   | <i>T</i> = 120 °C; <i>t</i> = 5 min | - Highly soluble lignins in pMDI<br>- No solvent<br><br>- Cat. Free<br>- Short curing time  | - Low lignin %<br><br>- Toxic reagents for lignin methylation                     | Sumerskii <i>et al.</i> <sup>23</sup> |
| 3     | Alkali lignin  | Lignin : TDI : PEG (n. a.)                            | Solvent: THF; Cat.: stannous octanoate                                       | <i>T</i> = r.t.; <i>t</i> = 48 h    | - No lignin modification requested  | - Low lignin %<br>- Toxic solvent<br>- Catalyst needed<br>- Long curing time      | Chahar <i>et al.</i> <sup>76</sup>    |
| 4     | Kraft, organosolv, steam explosion, acid hydrolysis and hydroxyalkyl lignins | Lignin : pMDI (0.6 : 0.4)                             | Additive: H <sub>2</sub> O or emulsifying agent (Scripset 700); Solvent: MEK | <i>T</i> = 27 °C; <i>t</i> = 36 h   | - No lignin modification requested<br>- Different lignin substrates   | - Toxic solvents  | Glasser <i>et al.</i> <sup>77</sup>   |
| 5     | Kraft and alkali lignins PO copolymers (LPO)                                 | LPPO : pMDI : HDI (n. a.)                             | Solvents: benzene or DMF   | <i>T</i> = 105 °C; <i>t</i> = n.a.  | - Different lignin substrates   | - Very toxic/carcinogenic solvents<br>- Use of additives<br>- Two-steps procedure | Glasser <i>et al.</i> <sup>78</sup>   |
| 6     | Kraft  | Lignin : CO : MDI (0.1 : 0.3 : 0.6)                   | None   | <i>T</i> = r.t.; <i>t</i> = 7 days  | - No additives  | - Very low lignin content   | Tavares <i>et al.</i> <sup>75</sup>   |

<sup>a</sup> Components of the adhesive formulation in addition to lignin. List of abbreviations: TDI = toluene diisocyanate; THF = tetrahydrofuran; HDI = hexamethylene diisocyanate; PO = propylene oxide; DMF = dimethyl formamide; CO = castor oil; n.a. = not available.


diffusion edited <sup>1</sup>H experiment uses a non-quantitative pulse program which significantly overestimates signals of lower molecular weight compounds,<sup>31</sup> cross validation of the values obtained from chromatography analyses (see above) was not possible. Comparison of the relative intensities of the lignin peaks observed in the solid state <sup>13</sup>C NMR spectrum (Fig. S12<sup>†</sup>) with the signals apparent in the solution state spectra (Fig. S17<sup>†</sup>) suggested that the insolubles predominantly consisted of fractions with high residual lignin content.

To further investigate if the modification occurred on cellulose, hemicellulose or lignin – all present in the RS after REX – the residual lignin content was removed by extractive ball milling or bleaching (more details are given in the ESI<sup>†</sup>). In the lignins isolated through ball milling a relatively strong ethoxy CH<sub>3</sub> peak indicated a derivatization during REX (see Fig. S23<sup>†</sup>). The obtained cellulosic fraction after ball milling proved to be completely insoluble in the electrolyte system,

presumably due to strong mechanical cross linking, thereby preventing comparison of the spectra.

The bleached sample gave completely dissolved NMR samples and showed that even after the removal of lignin a small ethoxy CH<sub>3</sub> peak remained, proving that also the polysaccharide fractions were at least slightly modified during REX. The shape of the peak slightly changed with the disappearance of a shoulder at lower frequencies (around 1.0 ppm), presumably caused by the removed lignin ethoxy moieties. Investigation of the HSQC spectrum and comparison with the unbleached sample showed that the polysaccharide fractions were not visibly affected by the bleaching. There were no signs of etherification reactions in the cellulose backbone when comparing the obtained <sup>1</sup>H-<sup>13</sup>C HSQC spectra with the thorough reports on methylcelluloses.<sup>79</sup> However, given the apparent rather minor overall derivatization and high viscosity of the sample necessitating a reduction of the measuring con-



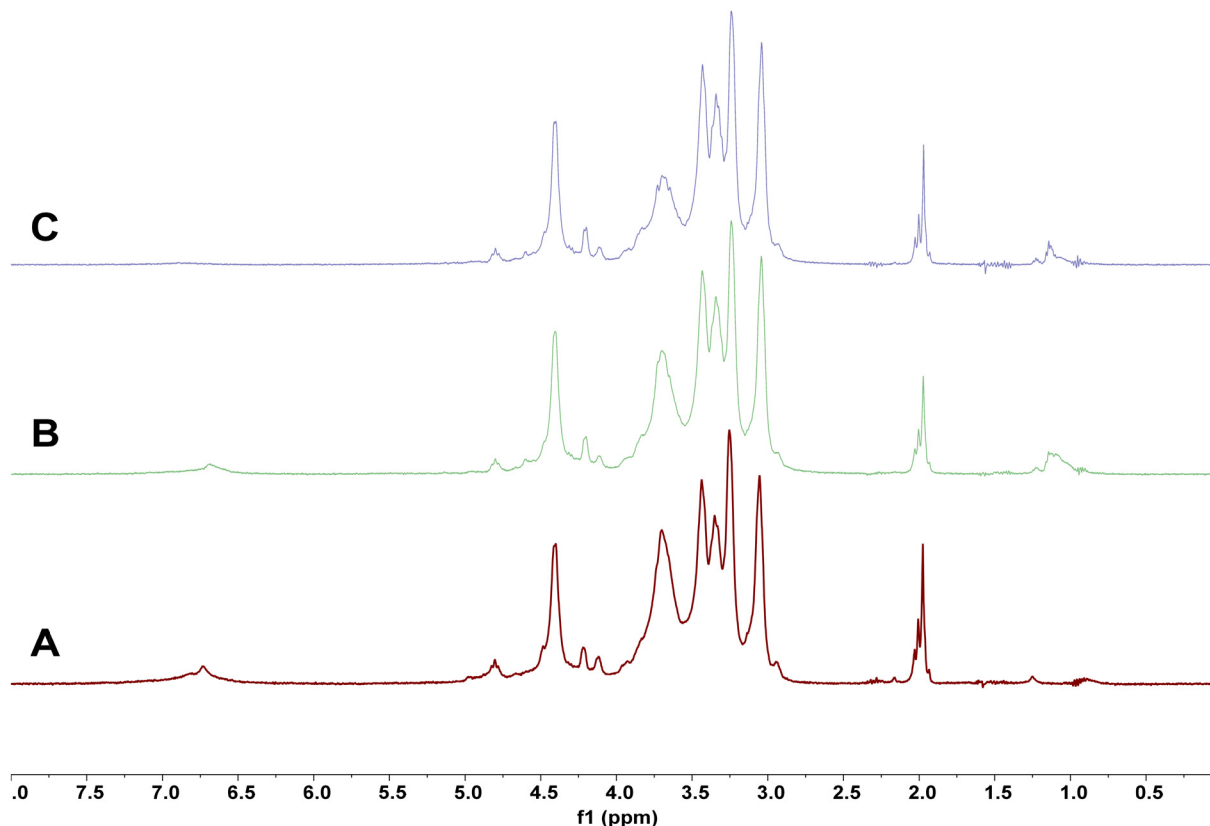

**Fig. 5** Stack of diffusion edited  $^1\text{H}$  spectra ( $[\text{P}_{4444}][\text{OAc}] : \text{DMSO-}d_6$ , 1 : 4 wt%; 400 MHz; 65 °C) of cellulose-rich solids (measuring concentration 2.5 wt%) obtained on the RS of the S-500 control sample (A), RS after reactive extraction with the highest DS (conditions:  $[\text{EtOH}] = 99\%$ ,  $[\text{H}_2\text{SO}_4] = 0.15 \text{ M}$ ,  $t = 4 \text{ h}$ ) unbleached (B) and bleached (C). Despite the presence of insolubles in the measuring solutions, spectra A and B were not drastically different from previous reports on pulp samples obtained in used or similar electrolytes. Comparing spectra A and B it becomes evident that higher severity factors lead to the incorporation of ethoxy functionalities also in the polymeric fractions according to an additional peak at around 1 ppm characteristic of an ethoxy  $\text{CH}_3$  moiety. After additional bleaching of the high severity HTT solid (C) the lignin fractions are effectively removed, while the ethoxy peak at least partly remains. This indicates that the modification partially occurred on the polysaccharide fractions of the RS, presumably on the hemicelluloses.

centration, the absence can admittedly also be ascribed to the insufficient signal to noise ratio. As expected for a hardwood pulp, the hemicellulose fractions predominantly consisted of xylans with a high proportion of acetylated moieties, indicated by four distinct peaks for acetyl  $\text{CH}_3$  groups at around 2 ppm in the diffusion edited  $^1\text{H}$  spectra. While the peaks appear almost as intensive as the cellulose backbone, it should be noted that the signals obtained in this pulse program are heavily influenced by the relaxation times of the functionalities and the molecular weight of the polymer. In pulp samples the intensities of hemicellulose constituents can thus be drastically overestimated.<sup>31</sup> Given the low peak intensities of the ethoxy  $\text{CH}_3$  moiety and the absence of signals of a modified cellulose backbone, we suspect that the ethoxylation during REx of the polysaccharide fractions of the RS is also predominantly occurring on the xylans. Although we admittedly do not have solid proof for this assumption, the carboxylic acid functionalities, *e.g.*, of the methylglucuronic acid sidechains represent a favorable side of attack through esterification.

In conclusion, the ethoxy functionalities in the RS determined by chromatography methods, are likely predominantly present in non-extractable lignin fractions and to a low extent in the hemicelluloses.

## Conclusions

Reactive extraction (REx) allowed the isolation of ethoxylated lignins in yields up to 52% with respect to the initial lignin content with a DS of up to 40.8/100 Ar. The effects of process parameters, *i.e.*, reaction time, solvent (EtOH) and catalyst ( $\text{H}_2\text{SO}_4$ ) concentration, on the lignin structure and properties have been thoroughly discussed. An increase of the solvent and catalyst concentration improved the incorporation of EtO-groups, while decreasing the molar mass and  $T_g$  of the lignin samples. NMR experiments of RELs showed that REx causes ethoxylation and esterification of aliphatic  $-\text{OH}$  groups while phenolic  $-\text{OH}$  groups are not affected. Moreover, the analysis of the cellulose-rich fraction by wet chemistry and NMR





approaches showed that ethoxylation also partially occurs in the polysaccharide fraction. Comparing different methods (HI-based vs. NMR) of ethoxy group quantification in lignin revealed that quantitative  $^{13}\text{C}$  NMR works best for the quantification of the total ethoxy group (ethers and esters) content. On the other hand, the HI method based on HS GC-MS is the best for the quantification of ethoxy-ethers. Furthermore, utilizing ethoxylated lignins could improve the performance of lignin-based PU adhesives.

The major strength of the REX approach is its simplicity. REX allows for a simultaneous functionalization and extraction of lignin from hydrothermally treated wooden biomass. This avoids tedious steps of lignin separation from biomass prior to functionalization. In addition, the use of non-toxic and inexpensive reagents, *i.e.*, ethanol and sulfuric acid—which can be almost fully recycled—opens the potential of the production of highly ethoxylated lignins on an industrial scale.

To summarize, different concomitant aspects are decisive for the high yield production of highly ethoxylated lignins:

(i) The hydrothermal treatment carried out before REX allowed biomass component fractionation, making lignin easily accessible by the ethanol solvent-reagent during REX.

(ii) As discussed throughout the text, ethoxylation occurs mostly at the  $\alpha$ -position of  $\beta$ -O-4 bonds. Based on our previous reports,<sup>8,9</sup> the combination of a low liquid-to-solid ratio ( $L/S = 1$ ) and low severity ( $P$ -factor = 500) leads to the isolation of  $\beta$ -O-4 rich lignins. Thus, the high number of  $\beta$ -O-4 moieties maintained after the hydrothermal treatment favored the occurrence of ethoxylation at the  $\alpha$ -position of  $\beta$ -O-4 moieties.

(iii) The comprehensive investigation of the effects of process parameters ( $t$ , [EtOH], and catalyst amount) on the degree of substitution allowed for an optimization of the process targeting both high lignin yield and high degree of substitution with ethoxy groups. Overall, we found that to achieve highly ethoxylated lignin, the purity of ethanol is the most crucial parameter, while the time and the catalyst amount affect the outcome to a minor extent.

(iv) Ethoxylation of extractives was hypothesized as an additional contribution to the number of ethoxy groups in RELs. This will be further confirmed by dedicated future studies.

In light of all these considerations, in our vision, REX is a general approach which can be applied for the production of ethoxylated lignins starting from various biomass sources. More specifically, to enhance the degree of substitution, pure solvents should be used with low catalyst loading for a short time. In addition, to further highlight the general potential of REX, other modifications (*i.e.*, acetylation) may be developed in future studies.

## Author contributions

D.R.: investigation, conceptualization, funding acquisition, supervision, and writing – review & editing; N.K.: investigation, methodology, and writing – original draft; L.F.: investigation,

methodology, and writing – original draft; D.D.: investigation and methodology; M.C.: investigation and methodology; I.S.: investigation and methodology; M.H.: funding acquisition, supervision, and review & editing; A.P.: funding acquisition, supervision, and review & editing; M.B.: funding acquisition and supervision.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

The authors thank Madina Muratova (Aalto University) for her help in the compositional analysis of wood solids and Oliver Musl (Institute of Chemistry of Renewable Resources; BOKU, Vienna) for the useful discussion and feedback. D. R. gratefully acknowledges the support from the Academy of Finland's Flagship Programme under Projects No. 318890 and 318891 (Competence Center for Materials Bioeconomy, FinnCERES). D. D., M. C. and M. B. gratefully acknowledge the support from the Academy of Finland (grant 341586). D. R. acknowledges FinnCERES for its support through GoGlobal mobility fundings.

## References

- 1 F. G. Calvo-flores and J. A. Dobado, *ChemSusChem*, 2010, **3**, 1227.
- 2 L. Dessbesell, M. Paleologou, M. Leitch, R. Pulkki and C. (Charles) Xu, *Renewable Sustainable Energy Rev.*, 2020, **123**, 109768.
- 3 F. S. Chakar and A. J. Ragauskas, *Ind. Crops Prod.*, 2004, **20**, 131–141.
- 4 M. Karlsson, V. L. Vegunta, R. Deshpande and M. Lawoko, *Green Chem.*, 2022, **24**, 1211.
- 5 Y. Wang, P. Liu, G. Zhang, Q. Yang, J. Lu, T. Xia, L. Peng and Y. Wang, *Renewable Sustainable Energy Rev.*, 2021, **137**, 110586.
- 6 R. Zhang, H. Gao, Y. Wang, B. He, J. Lu, W. Zhu, L. Peng and Y. Wang, *Bioresour. Technol.*, 2023, **369**, 128315.
- 7 M. Y. Balakshin, E. A. Capanema, I. Sulaeva, P. Schlee, Z. Huang, M. Feng, M. Borghei, O. J. Rojas, A. Potthast and T. Rosenau, *ChemSusChem*, 2021, **14**, 1016.
- 8 D. Tarasov, P. Schlee, A. Pranovich, A. Moreno, L. Wang, D. Rigo, M. H. Sipponen, C. Xu and M. Balakshin, *Green Chem.*, 2022, **24**, 6639.
- 9 P. Schlee, D. Tarasov, D. Rigo and M. Balakshin, *ChemSusChem*, 2023, **16**, e2023005.
- 10 J. H. Lora and W. G. Glasser, *J. Polym. Environ.*, 2002, **10**, 39.
- 11 D. A. Baker and T. G. Rials, *J. Appl. Polym. Sci.*, 2013, **130**, 713.
- 12 Y. Li and S. Sarkanen, *Macromolecules*, 2005, **38**, 2296.



- 13 S. Laurichesse and L. Avérous, *Prog. Polym. Sci.*, 2014, **39**, 1266.
- 14 M. Zhang and A. A. Ogale, *Carbon*, 2013, **69**, 626.
- 15 W. G. Glasser, *Front. Chem.*, 2019, **7**, 1.
- 16 D. Di Francesco, C. Dahlstrand, J. Löfstedt, A. Orebom, J. Verendel, C. Carrick, Å. Håkansson, S. Eriksson, H. Rådberg, H. Wallmo, M. Wimby, F. Huber, C. Federsel, M. Backmark and J. S. M. Samec, *ChemSusChem*, 2021, **14**, 2414.
- 17 D. Di Francesco, D. Rigo, R. Baddigam, A. P. Mathew, N. Hedin, M. Selva and J. S. M. Samec, *ChemSusChem*, 2022, **15**, e2022003.
- 18 X. Meng, S. Bhagia, Y. Wang, Y. Zhou, Y. Pu, J. R. Dunlap, L. Shuai, A. J. Ragauskas and C. G. Yoo, *Ind. Crops Prod.*, 2020, **146**, 112144.
- 19 O. Hosseinaei, D. P. Harper, J. J. Bozell and T. G. Rials, *Int. J. Mol. Sci.*, 2017, **18**, 1410.
- 20 Y. Huang, S. Sun, C. Huang, Q. Yong, T. Elder and M. Tu, *Biotechnol. Biofuels*, 2017, **10**, 1–11.
- 21 S. Kubo and J. F. Kadla, *Macromolecules*, 2004, **37**, 6904.
- 22 C. Chew, *Solvolytic extraction of lignin from wood*, Department of Chemistry McGill University, Montreal, Canada, 1968.
- 23 I. Sumerskii, P. Solt, H. W. G. Van Herwijnen, I. Sulaeva, T. Thomas, T. Rosenau and A. Potthast, *Lenzinger Ber.*, 2022, **97**, 109.
- 24 X. Jiang, Z. Tian, X. Ji, H. Ma, G. Yang and M. He, *Int. J. Biol. Macromol.*, 2022, **201**, 400.
- 25 H. Sadeghifar, C. Cui and D. S. Argyropoulos, *Ind. Eng. Chem. Res.*, 2012, **51**, 16713.
- 26 M. Y. Balakshin, E. A. Capanema, M. Colakyan and F. Lipiecki, *US Patent Nr 10240006B2*, 2019.
- 27 M. Karlsson, N. Giummarella, A. Lind and M. Lawoko, *ChemSusChem*, 2020, **13**, 4666.
- 28 S. Bertella and J. S. Luterbacher, *Green Chem.*, 2021, **23**, 3459.
- 29 L. Shuai, M. T. Amiri, Y. M. Questell-Santiago, F. Héroguel, Y. Li, H. Kim, R. Meilan, C. Chapple, J. Ralph and J. S. Luterbacher, *Science*, 2016, **354**, 329.
- 30 D. S. Zijlstra, C. W. Lahive, C. A. Analbers, M. B. Figueireido, Z. Wang, C. S. Lancefield and P. J. Deuss, *ACS Sustainable Chem. Eng.*, 2020, **8**, 5119.
- 31 L. Fliri, K. Heise, T. Koso, A. R. Todorov, D. Rico, S. Hietala, J. Fiskari, I. Kilpeläinen, M. Hummel and A. W. T. King, *Nat. Protoc.*, 2023, **18**, 2084.
- 32 Y. Ni and Q. Hu, *J. Appl. Polym. Sci.*, 1995, **57**, 1441–1446.
- 33 H. Goto, K. Koda, G. Tong, Y. Matsumoto and G. Meshitsuka, *J. Wood Chem. Technol.*, 2006, **26**, 81.
- 34 I. Sumerskii, T. Zweckmair, H. Hettegger, G. Zinovyev, M. Bacher, T. Rosenau and A. Potthast, *RSC Adv.*, 2017, **7**, 22974.
- 35 C. S. Lancefield, H. L. J. Wienk, R. Boelens, B. M. Weckhuysen and P. C. A. Bruijninx, *Chem. Sci.*, 2018, **9**, 6348.
- 36 M. Balakshin, E. Capanema, H. Gracz, H. Min Chang and H. Jameel, *Planta*, 2011, **233**, 1097.
- 37 M. Y. Balakshin, E. A. Capanema and H. M. Chang, *Holzforschung*, 2007, **61**, 1.
- 38 M. Y. Balakshin, E. A. Capanema, C.-L. Chen and H. S. Gracz, *J. Agric. Food Chem.*, 2003, **51**, 6116.
- 39 J. Ralph and L. L. Landucci, *Lignin and Lignans: Advances in Chemistry*, 2010, pp. 137–243.
- 40 M. M. Abu-Omar, G. T. Beckham, J. S. Luterbacher, J. Ralph, R. Rinaldi, Y. Roman-Leshkov, J. S. M. Samec, B. F. Sels and F. Wang, *Energy Environ. Sci.*, 2021, **14**, 262.
- 41 A. Granata and D. S. Argyropoulos, *J. Agric. Food Chem.*, 1995, **43**, 1538.
- 42 M. Balakshin and E. Capanema, *J. Wood Chem. Technol.*, 2015, **35**, 220.
- 43 G. Zinovyev, I. Sulaeva, S. Podzimek, D. Rössner, I. Kilpeläinen, I. Sumerskii, T. Rosenau and A. Potthast, *ChemSusChem*, 2018, **11**, 3259.
- 44 A. Sluiter, B. Hames, R. Ruiz, C. Scarlata, J. Sluiter, D. Templeton and D. Crocker, *Determination of Structural Carbohydrates and Lignin in Biomass*, 2005.
- 45 T. Koso, D. R. del Cerro, S. Heikkinen, T. Nypelö, J. Buffiere, J. E. Perea-Buceta, A. Potthast, T. Rosenau, H. Heikkinen, H. Maaheimo, A. Isogai, I. Kilpeläinen and A. W. T. King, *Cellulose*, 2020, **27**, 7929.
- 46 A. W. T. King, V. Ma, S. A. Kedzior, T. Laaksonen, G. J. Partl, S. Heikkinen, H. Koskela, H. A. Heikkinen, A. J. Holding, E. D. Cranston and I. Kilpela, *Biomacromolecules*, 2018, **19**, 2708.
- 47 P. Solt, S. Libowitzky and H. W. G. Van Herwijnen, *Wood Sci. Technol.*, 2020, **54**, 7.
- 48 D. Tarasov, M. Leitch and P. Fatehi, *Biotechnol. Biofuels*, 2018, **11**, 1.
- 49 R. El, N. Brosse, P. Sannigrahi and A. Ragauskas, *Polym. Degrad. Stab.*, 2010, **95**, 997.
- 50 K. Sutoh, K. Kobata and T. Watanabe, *J. Agric. Food Chem.*, 2001, **49**, 4026.
- 51 S. S. Mochalov, A. N. Fedotov, E. V. Trofimova and N. S. Zefirov, *Russ. J. Org. Chem.*, 2016, **52**, 503.
- 52 S. Ralph, U. F. Service and J. Ralph, *NMR Database of Lignin and Cell Wall Model Compounds*, 2009.
- 53 M. Y. Balakshin, E. A. Capanema, X. Zhu, I. Sulaeva, A. Potthast, T. Rosenau and O. J. Rojas, *Green Chem.*, 2020, **22**, 3985–4001.
- 54 K. Tanaka, *Chem. Pharm. Bull.*, 1977, **57**, 364–370.
- 55 [https://www.chemicalbook.com/SpectrumEN\\_103-73-1\\_1HNMR.htm](https://www.chemicalbook.com/SpectrumEN_103-73-1_1HNMR.htm) (Accessed: 29/09/2023).
- 56 E. Adler, *Wood Sci. Technol.*, 1977, **11**, 169.
- 57 M. Y. Balakshin and E. A. Capanema, *RSC Adv.*, 2015, **5**, 87187.
- 58 B. G. J. Leary, D. A. Sawtell and H. Wong, *Holzforschung*, 1983, **37**, 213.
- 59 J. Sipilä and G. Brunow, *Holzforschung*, 1991, **45**, 275.
- 60 G. Brunow, J. Sipilä and T. Mäkelä, *Holzforschung*, 1989, **43**, 55.
- 61 F. Lu and J. Ralph, *Org. Biomol. Chem.*, 2008, **6**, 3681.
- 62 E. A. Capanema, M. Y. Balakshin and J. F. Kadla, *J. Agric. Food Chem.*, 2005, **53**, 9639.



- 63 H. Li, X. Chai, M. Liu and Y. Deng, *J. Agric. Food Chem.*, 2012, **60**, 5307.
- 64 S. M. Baker, *Holzforschung*, 1996, **50**, 573.
- 65 T. J. McDonough, *The Chemistry of Organosolv Delignification, IPST Technical Paper Series No. 455*, 1992.
- 66 A. S. Jääskeläinen, T. Liitiä, A. Mikkelsen and T. Tamminen, *Ind. Crops Prod.*, 2017, **103**, 51.
- 67 X. Pan, J. F. Kadla, K. Ehara, N. Gilkes and J. N. Saddler, *J. Agric. Food Chem.*, 2006, **54**, 5806.
- 68 J. R. Meyer, H. Li, J. Zhang and M. B. Foston, *ChemSusChem*, 2020, **13**, 4557.
- 69 W. M. Goldmann, J. Ahola, M. Mikola and J. Tanskanen, *Sep. Purif. Technol.*, 2019, **209**, 826.
- 70 B. S. Kubo, Y. Uraki and Y. Sano, *Holzforschung*, 1996, **50**, 144–150.
- 71 S. Sen, S. Patil and D. S. Argyropoulos, *Green Chem.*, 2015, **17**, 4862.
- 72 A. Vishtal and A. Kraslawski, *BioResources*, 2011, **6**, 3547.
- 73 M. Alinejad, S. Nikafshar, A. Gondaliya, S. Bagheri, N. Chen, S. K. Singh, D. B. Hodge and M. Nejad, *Polymers*, 2019, **11**, 1202.
- 74 D. Diment, O. Tkachenko, P. Schlee, N. Kohlhuber, A. Potthast, T. Budnyak, D. Rigo and M. Balakshin, *Biomacromolecules*, 2024, **25**(1), 200.
- 75 L. B. Tavares, C. V. Boas, G. R. Schleder, A. M. Nacas, D. S. Rosa and D. J. Santos, *eXPRESS Polym. Lett.*, 2016, **10**, 927.
- 76 S. Chahar, M. G. Dastidar, V. Choudhary and D. K. Sharma, *J. Adhes. Sci. Technol.*, 2004, **18**, 169.
- 77 W. H. Newman and W. G. Glasser, *Holzforschung*, 1985, **39**, 345.
- 78 W. G. Glasser, V. P. Saraf and W. H. Newman, *J. Adhes.*, 1982, **14**, 233.
- 79 H. Kono, S. Fujita and K. Tajima, *Carbohydr. Polym.*, 2017, **157**, 728.

