

Cite this: *J. Mater. Chem. A*, 2024, 12, 968

Solvation structure regulation of an organic small molecule additive for dendrite-free aqueous zinc-ion batteries†

Xiaomin Li,^{‡a} Jinwei Miao,^{‡b} Fulong Hu,^a Kang Yan,^b Lin Song,^{Ⓜa} Huiqing Fan,^{Ⓜb} Longtao Ma^c and Weijia Wang^{Ⓜ*b}

The aqueous zinc-ion battery is a potential energy storage device due to its environmental sustainability and cost-effectiveness. Nonetheless, the reduced reversibility of the Zn anode arising from continuous parasitic reactions (hydrogen evolution reaction (HER) and corrosion) and random dendrite growth has a significant impact on its life and performance. Herein, organic small-molecule formamide (FA) is proposed as an additive to the aqueous ZnSO₄ electrolyte and realizes a dendrite-free and highly reversible Zn anode by regulating the solvation structure. Through theoretical calculation, as well as physicochemical and electrochemical characterization, it is evidenced that FA additive shows the following characteristics: (1) it replaces some of the H₂O molecules in the solvation structure to participate in the solvation structure of Zn²⁺, and significantly inhibit the HER, (2) breaks the original hydrogen bonding network, resulting in the improvement of the low temperature performance of the battery, (3) preferentially adsorbs on the Zn surface to regulate the charge distribution at the Zn anode/electrolyte interface and inhibit Zn corrosion during the initial cycling process, and (3) contributes to the formation of an inorganic–organic double-layer solid electrolyte interface (SEI) for dendrite-free uniform zinc deposition. Benefiting from these advantages, Zn||Cu asymmetric batteries assembled with this electrolyte show more than 1700 highly reversible zinc plating/stripping cycles, and the average coulombic efficiency reaches 99.24%. Zn||Zn symmetric batteries survive more than 1600 h of stable cycling at 1 mA cm⁻² and 0.5 mA h cm⁻². As a proof of concept, the Zn||MnO₂ full cells provide excellent cycle performance over 2000 cycles at the current density of 4 A g⁻¹, and maintain a high capacity retention of 85.1%.

Received 25th September 2023
Accepted 27th November 2023

DOI: 10.1039/d3ta05814j

rsc.li/materials-a

1. Introduction

Aqueous zinc-ion batteries have the advantages of high safety, low cost and non-toxicity,^{1–4} while their continuous electrochemical corrosion induced by the aqueous electrolyte and the resulting low reversibility of the Zn anode encumber their further applications.^{5–9} Specifically, when the battery is at rest or in operation, the solvated Zn²⁺ near the electric double-layer (EDL) structure needs to overcome an energy barrier to desolvate and to release a large number of electrochemically reactive H₂O molecules. The reactive H₂O molecules lead to the

evolution of H⁺ into H₂ and the variation of local pH values, which will attack the metallic Zn and trigger parasitic side reactions. As a results, a heterogeneous zinc surface and a porous structure is formed, which inevitably exacerbate the chemical corrosion of the Zn anode during repeated plating/stripping processes.^{10–12} Meanwhile, loose Zn particles with irregular morphology lead to the loss of electrical contact between the deposited Zn and the substrate, further deteriorating the reversibility of the Zn anode.¹³ To make matters worse, irregularly shaped zinc dendrite particles tend to puncture the separator, resulting in a short circuit in the battery.^{14–16} To alleviate the above problems, researchers have proposed strategies such as constructing artificial interfacial layers,¹⁷ modifying collectors,¹⁸ optimizing the internal structure of the zinc anode,¹⁹ modifying the separator,²⁰ and increasing the salt concentration²¹ to protect the Zn anode from the deleterious reactions associated with aqueous electrolyte. While these methods provide new insights into zinc metal protection, they are difficult to implement from the perspective of manufacturing process and production cost.²² Considering the above difficulties, it would be more practical to explore suitable electrolyte additives to inhibit the formation of dendrites and to

^aFrontiers Science Center for Flexible Electronics, Institute of Flexible Electronics, Northwestern Polytechnical University, Xi'an 710072, P. R. China

^bState Key Laboratory of Solidification Processing, School of Materials Science and Engineering, Northwestern Polytechnical University, Xi'an 710072, P. R. China. E-mail: weijia.wang@nwpu.edu.cn

^cSchool of Materials Science and Engineering, Guangdong Provincial Key Laboratory of Advanced Energy Storage Materials, South China University of Technology, Guangzhou 510641, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ta05814j>

‡ Xiaomin Li and Jinwei Miao contributed equally to this work.

improve the reversibility of the Zn anode.^{23–26} Currently, the commonly used electrolyte additives for aqueous zinc-ion batteries can be categorized into four types, including ionic, organic, inorganic, and metallic additives.^{27,28} Among them, organic additives have attracted wide attention due to their high solubility in aqueous solution and unique regulation mechanisms.^{11,24,29}

Most electrolyte additive engineering strategies are based on regulating the solvation structure of the Zn²⁺ hydration layer [Zn(H₂O)₆²⁺], which reduces the solvation effect between Zn²⁺ and H₂O molecules, thus inhibiting the side reactions. In addition, the regulation of solvation structure can affect the desolvation and nucleation processes of Zn²⁺, leading to a more uniform deposition of zinc.³⁰ These organic solvents are mixed with aqueous solvents to form a mixed electrolyte that retains the inherent advantages of each system, namely non-flammability and non-toxicity of the aqueous system and the improved electrochemical stability of the non-aqueous system.³¹ Using organic solvents successfully resolves the conflict between performance, cost, interface chemistry, sensitivity to ambient humidity, and environmental friendliness. In mixed electrolytes, it is necessary to make a reasonable selection of organic molecules.³² Generally speaking, organic molecules need to have a strong polarity (usually containing N, O, F, and their lone pair electrons can be coordinated with metal ions); be miscible with water and form strong hydrogen bonds and reduce the activity of water; contain functional groups that can participate in chemical reactions and be reduced to form a dense solid electrolyte interface (SEI). As an example, Wang *et al.* reported a ZnCl₂/H₂O–DMSO electrolyte by introducing the organic additive DMSO into the ZnCl₂ aqueous electrolyte.³³ Since the donor number of DMSO (29.8) is much higher than that of H₂O (18), the solvation structure of Zn²⁺ preferentially combines with DMSO and therefore alters the hydrated Zn²⁺ solvation structure. During zinc deposition, DMSO is more likely reduced to generate a dense Zn₁₂(SO₄)₃Cl₃(OH)₁₅–5H₂O–ZnSO₃–ZnS SEI, which inhibits the decomposition of solvated H₂O. In addition, the activation of H₂O is greatly reduced, due to the enhanced interaction between H₂O and DMSO. All the phenomena above demonstrate that DMSO plays the role of inhibiting the passivation of the zinc surface, impeding the formation of zinc dendrites, and reducing the decomposition of H₂O. Triethyl phosphate (TEP) is also considered as a cosolvent with a strong solvation ability in aqueous/nonaqueous electrolytes. TEP has a higher donor number (26 kcal mol^{–1}) than H₂O (18 kcal mol^{–1}) and tends to form an inner solvation structure occupied by TEP around Zn²⁺ with a strong interaction of H-bonds. The coordination structure of TEP can reduce water activity to inhibit cathode dissolution and form a solid polymer–inorganic interphase with composition of poly-ZnP₂O₆ and ZnF₂ to effectively prevent Zn dendrite growth and parasitic HER. Meanwhile, organic solvents such as TEP and trimethyl phosphate (TMP) can still maintain the safety of aqueous electrolytes and improve the reversibility of Zn.³⁴ Acrylamide (AM) was introduced into a high-voltage aqueous electrolyte for aqueous Zn-ion batteries, in which small dipole molecules replace part of the water molecules and participate in the

solvation structure of Zn²⁺, thus reducing the activity of water and expanding the ESW. In addition, these dipole molecules can form hydrogen bonds with water molecules and disrupt the hydrogen bond network, thereby reducing parasitic reactions associated with water molecules.³⁵ It is of great importance to develop easier-to-handle and environmentally friendly organic additives with excellent zincophilicity. Regulating the solvation structure can provide experience in electrolyte development engineering, as well as guidance for the rational design of a stable and reversible Zn anode.²⁴

In this work, a simple electrolyte additive engineering strategy is developed by introducing formamide (FA) into ordinary ZnSO₄ electrolytes to modulate the surface chemistry of the Zn anode and bulk electrolyte structure. For the unprotected Zn anode, Zn²⁺ tends to nucleate at protrusions with low nucleation potentials, which inevitably leads to deterioration of dendrites. Due to the strong interaction between the carbonyl group (C=O) of the FA molecule and the zinc atoms on the surface of the Zn anode, a hydrophobic interface is formed, which reduces the reactivity of H₂O with the Zn anode. This unique metal–molecule interface acts as a corrosion inhibitor against water-induced side reactions, resulting in a corrosion-free Zn anode that avoids worsening of the tip effect. Meanwhile, the lone pair electrons on the O element make FA zincophilic and provide rich sites to coordinate with Zn²⁺, which fundamentally reduces the activity of H₂O and inhibits the HER, thus improving the quality of zinc deposition. In addition, FA molecules are preferentially reduced over H₂O molecules, resulting in the *in situ* generation of an SEI, which realizes a good protective effect on the Zn anode.

2. Experimental

MnO₂ cathode materials are prepared by the hydrothermal method. 2.67 mmol (0.403 g) of MnSO₄ and 16 mmol (2.529 g) of KMnO₄ are added into 70 ml of deionised water and stirred until the reactants are completely dissolved. The solution is transferred into a hydrothermal kettle and reacted at 160 °C for 12 h. The suspension is collected and washed with deionized water and anhydrous ethanol several times to remove impurities, finally the MnO₂ product is obtained by drying at 60 °C.³⁶ The physical characterization of the zinc foils, by-products and SEI is mainly carried out by X-ray diffraction (XRD) and X-ray photoelectron spectroscopy (XPS). The coordination state of Zn²⁺ in aqueous solution is detected by Raman spectroscopy and Fourier transform infrared spectroscopy (FTIR). The surface morphology of the zinc foils is observed using a Field Emission Scanning Electron Microscope (FESEM), and the SEI is observed by transmission electron microscopy (TEM). The manufactured CR2032 coin cells are subjected to galvanostatic charge–discharge (GCD) tests using battery test systems. The electrochemical tests are all performed using an electrochemical workstation *via* techniques such as linear scanning voltammetry (LSV), Tafel, chronoamperometry (CA), cyclic voltammetry (CV), and electrochemical impedance spectroscopy (EIS).

3. Results and discussion

FA, as an excellent organic solvent, has the advantages of high dielectric constant, strong polarity, low viscosity and fast ion diffusion. Herein, 2 M ZnSO_4 is chosen as the base electrolyte and 30% FA electrolyte is prepared by adjusting the volume ratio of FA to H_2O (volume ratio of FA: H_2O = 3 : 7). Similarly, electrolytes containing 10% FA, 20% FA, 40% FA and 50% FA are also prepared in the same way. As shown in Fig. S1,[†] the electrolyte with 50% volume fraction of FA crystallizes out after standing for one month, while others show a uniform dissolved state without significant change.

3.1 Zn^{2+} solvation structure and physicochemical properties of electrolytes

Firstly, the role of FA in regulating the solvation structure of Zn^{2+} is demonstrated by theoretical calculation.³⁷ Fig. 1a shows the electrostatic potential diagrams of the FA molecule and H_2O molecule. Obviously, similar to the O atom in the H_2O molecule, the carbonyl group (C=O) in FA has a negative potential, indicating that there is a strong electrostatic potential between Zn^{2+} and FA, which makes them attract each other. The evolution of the solvation structure of Zn^{2+} is investigated by molecular dynamics (MD) simulation, and the electrolyte with FA volume fraction of 30% is chosen for demonstration



Fig. 1 (a) Electrostatic potential diagram of formamide (FA) and H_2O molecules. Molecular dynamics (MD) simulation snapshots and typical Zn^{2+} solvation structure of (b) pure ZnSO_4 electrolyte and (c) ZnSO_4/FA electrolyte. Radial distribution function (RDF) plots of Zn^{2+} -O of (d) pure ZnSO_4 electrolyte and (e) ZnSO_4/FA electrolyte. (f) Binding energy of Zn^{2+} - H_2O , Zn^{2+} -FA, H_2O - H_2O , and H_2O -FA. Infrared spectra (g) and the corresponding enlarged view of ν - SO_4 and ν -H-O (h) of ZnSO_4 electrolytes without and with various concentrations of FA. (i) Raman spectra of ZnSO_4 electrolytes without and with various concentrations of FA. (j) Ionic conductivity and (k) Zn^{2+} transference number of ZnSO_4 electrolytes without and with various concentrations of FA.

(denoted as ZnSO_4/FA). Fig. 1b shows the snapshot of the MD simulation of the pure ZnSO_4 electrolyte and the typical solvation structure, where Zn^{2+} is found to coordinate with H_2O molecules and SO_4^{2-} anions to form the $[\text{Zn}(\text{H}_2\text{O})_{6-x}(\text{SO}_4)_x]^{2+}$ solvation structure. As presented in the snapshot of the MD simulation of ZnSO_4/FA electrolyte (Fig. 1c), a solvation structure consisting of Zn^{2+} coordinated with four H_2O molecules and two FA molecules is observed, indicating that FA molecules coordinate with Zn^{2+} and break the original solvation structure, *i.e.*, FA molecules replace some H_2O molecules to participate in the solvation structure of Zn^{2+} . The distribution of the nearest-neighbor molecules is investigated by the radial distribution function (RDF), and the differences between the solvation structure of Zn^{2+} in pure ZnSO_4 electrolyte and ZnSO_4/FA electrolyte are discussed quantitatively. As displayed in Fig. 1d and S2a,† for the pure ZnSO_4 electrolyte, Zn^{2+} is coordinated with 5.17 H_2O molecules and 0.83 SO_4^{2-} anions to form the $[\text{Zn}(\text{H}_2\text{O})_{5.17}(\text{SO}_4)_{0.83}]^{2+}$ solvation structure. Due to the introduction of FA additive, the peak at 2.05 Å can be attributed to $\text{Zn}^{2+}-\text{O}(\text{FA})$ (Fig. 1e), demonstrating the participation of FA molecules in the solvation structure of Zn^{2+} . To be precise, the Zn^{2+} primary solvation structure in the ZnSO_4/FA electrolyte consists of about 4.22 H_2O molecules, 0.53 FA molecules and 1.25 SO_4^{2-} anions (Fig. S2b†), expressed as $[\text{Zn}(\text{H}_2\text{O})_{4.22}(\text{FA})_{0.53}(\text{SO}_4^{2-})_{1.25}]^{2+}$. In addition, it is found that the amount of SO_4^{2-} coordinated with Zn^{2+} increased with the addition of FA, indicating a transformation of the electrolyte structure from the solvent separated ion pair (SSIP) to contact ion pair (CIP). The transformation of the average solvation structure of Zn^{2+} indicates a greatly reduced amount of solvated H_2O , thus mitigating the HER and hopefully protecting the Zn anode from surface corrosion. As shown in the linear scanning voltammetry (LSV) (Fig. S3†), the addition of FA leads to a lower HER potential as compared with pure ZnSO_4 electrolyte (from -0.139 V to -0.181 V vs. Zn^{2+}/Zn).

Density functional theory (DFT) calculation also illustrates the influence of FA additive on the primary solvation structure of Zn^{2+} . As displayed in Fig. 1f, the binding energy of the FA molecule with Zn^{2+} is stronger than that of H_2O (-2.87 eV vs. -1.72 eV), indicating that FA is more likely to replace the H_2O in the solvation structure.³⁸ Meanwhile, the binding energy between FA and H_2O (-0.35 eV) is higher than that between H_2O and H_2O (-0.28 eV), suggesting that H_2O inclines to bind with FA thereby damaging the H-bond network in the native electrolyte, thus lowering the freezing point and facilitating the operation of the batteries at low temperatures.

In order to better understand the interaction of FA with the components of the original ZnSO_4 electrolyte, Raman and Fourier transform infrared (FT-IR) tests are performed. Raman spectra of different electrolytes are shown in Fig. 1i. The peaks occurring near 980 cm^{-1} can be assigned to the $\nu\text{-SO}_4^{2-}$ band. Based on the classical Eigen-Tamm (ET) mechanism, these strong peaks can be divided into contact ion pairs (CIP) and solvent-separated ion pairs (SSIP).^{39,40} With the addition of FA, the peak of the $\nu\text{-SO}_4^{2-}$ band shifts to higher frequencies, and the proportion of CIPs gradually increases, which proves the transformation of solvation structure from SSIP to CIP. The detailed

results are displayed in Fig. S4.† The influence of FA molecules on the interaction between Zn^{2+} and SO_4^{2-} is further confirmed by FT-IR results (Fig. 1g and h). In addition to the FA molecule (1677.45 , 1387.64 , 1323.41 cm^{-1}), the stretching vibration of $\nu\text{-SO}_4^{2-}$ (ZnSO_4 1086.42 cm^{-1} , ZnSO_4/FA 1079.28 cm^{-1}) shows a redshift, suggesting an enhancement of the electrostatic coupling between Zn^{2+} and SO_4^{2-} , which further indicates the increase of the proportion of CIP.^{40,41} In addition, a distinct wide peak at $3000\text{--}3700$ cm^{-1} can be attributed to the O–H stretching vibration of H_2O , which can be further divided into three peaks, corresponding to strong hydrogen bonds (~ 3230 cm^{-1}), weak hydrogen bonds (~ 3450 cm^{-1}), and non-hydrogen bonds (~ 3620 cm^{-1}), respectively.^{42,43} For pure ZnSO_4 electrolyte, strong hydrogen bonds account for the highest proportion in the hydrogen bond environment, but with the addition of FA, the strong hydrogen bonds attenuated more significantly, and Fig. S5† shows the results of the three hydrogen bonds. We can see that with the increase of FA, the proportion of strong hydrogen bonds decreases from 83.03% to 80.03%, while the proportion of weak hydrogen bonds increases from 13.73% to 18.24%, and the proportion of non-hydrogen bonds is small and has little change. This indicates that the original H-bond network in water is weakened, resulting in the inhibition of the HER, but at the same time the ionic conductivity of the electrolyte may be affected. The local environment of ^1H from H_2O in different electrolyte solutions was further investigated by nuclear magnetic resonance (^1H NMR) measurements, as shown in Fig. S6.†⁴⁴ The ^1H chemical shift peak moves to a higher value after adding FA, which is mainly because the strong interaction between FA and H_2O molecules weakens the electron density around the protons in the H_2O molecules, which also demonstrates the changes in solvation structure and hydrogen bonding.

In order to investigate the effect of FA on ion transport, ionic conductivity and transference number are tested. As shown in Fig. 1j, the ionic conductivity in pure ZnSO_4 electrolyte is 45.9 mS cm^{-1} , which decreases to 33.8 , 24.6 , 17.3 , and 5.64 mS cm^{-1} with the increase of FA with a volume ratio of 10%, 20%, 30%, and 40%, respectively. This may be ascribed to the slow migration of cations due to elevated electrolyte viscosity with the addition of additives. The detailed results are shown in Fig. S7,† which is consistent with FT-IR results. As presented in Fig. 1k, the transference number of Zn^{2+} increases from 0.38 to 0.67 as FA increases (detailed results are shown in Fig. S8†). This suggests that addition of FA promotes mass transfer at the electrolyte/anode interface, thereby facilitating the deposition of Zn. Ionic conductivity is influenced by factors such as zinc salt, composition of solvent, temperature, *etc.* When zinc salt content and temperature are consistent, the composition of solvent plays a significant role. In general, the higher the solvent viscosity, the lower the ionic conductivity. The viscosity of ZnSO_4 electrolytes without and with various concentrations of FA is shown in Fig. S9.† As the FA volume fraction increases from 0 to 40%, the viscosity increases, resulting in a decrease in ionic conductivity. Regarding transfer numbers, the anion migration is greatly reduced due to the formation of a unique solvation structure, while the cation is less affected, therefore the transfer number of Zn^{2+} increases with the increase of FA

volume fraction.³³ As a result, the ionic conductivity and transfer numbers exhibit an opposite trend with the increase in concentration. In order to balance the adverse effects of the reduction of ion conductivity caused by FA additive, 30% addition is a relatively better choice. It possesses a high Zn^{2+} transference number and appropriate conductivity, so the electrolyte with FA volume ratio of 30% and pure ZnSO_4 electrolyte are investigated, denoted as ZnSO_4/FA and ZnSO_4 , respectively.

3.2 Adsorption of FA and optimized electrolyte/anode interface characteristics

The adsorption energies of H_2O and FA molecules on the surface of Zn are analyzed by density functional theory (DFT)

(Fig. 2a). Specifically, the adsorption energy of FA molecules on the Zn (002) (-0.77 eV) and (100) (-0.56 eV) planes is much lower than that of H_2O molecules on the Zn (002) (-1.45 eV) and (100) (-0.46 eV) planes. The adsorption energy calculation results demonstrate that the ZnSO_4/FA electrolyte has zincophilic properties. FA molecules replace the adsorbed H_2O dipoles at the anode/electrolyte interface in the aqueous system, which significantly reduces the amount of free water and leads to a poor H_2O metal/molecule interface. To verify the zincophilic properties of FA molecules, the contact angle of the electrolytes on the surface of zinc foil is tested (Fig. 2b). It is found that the contact angle of ZnSO_4/FA electrolyte (99.11°) is smaller than that of pure ZnSO_4 electrolyte (102.12°), indicating that the addition of FA improves the zincophilic properties of

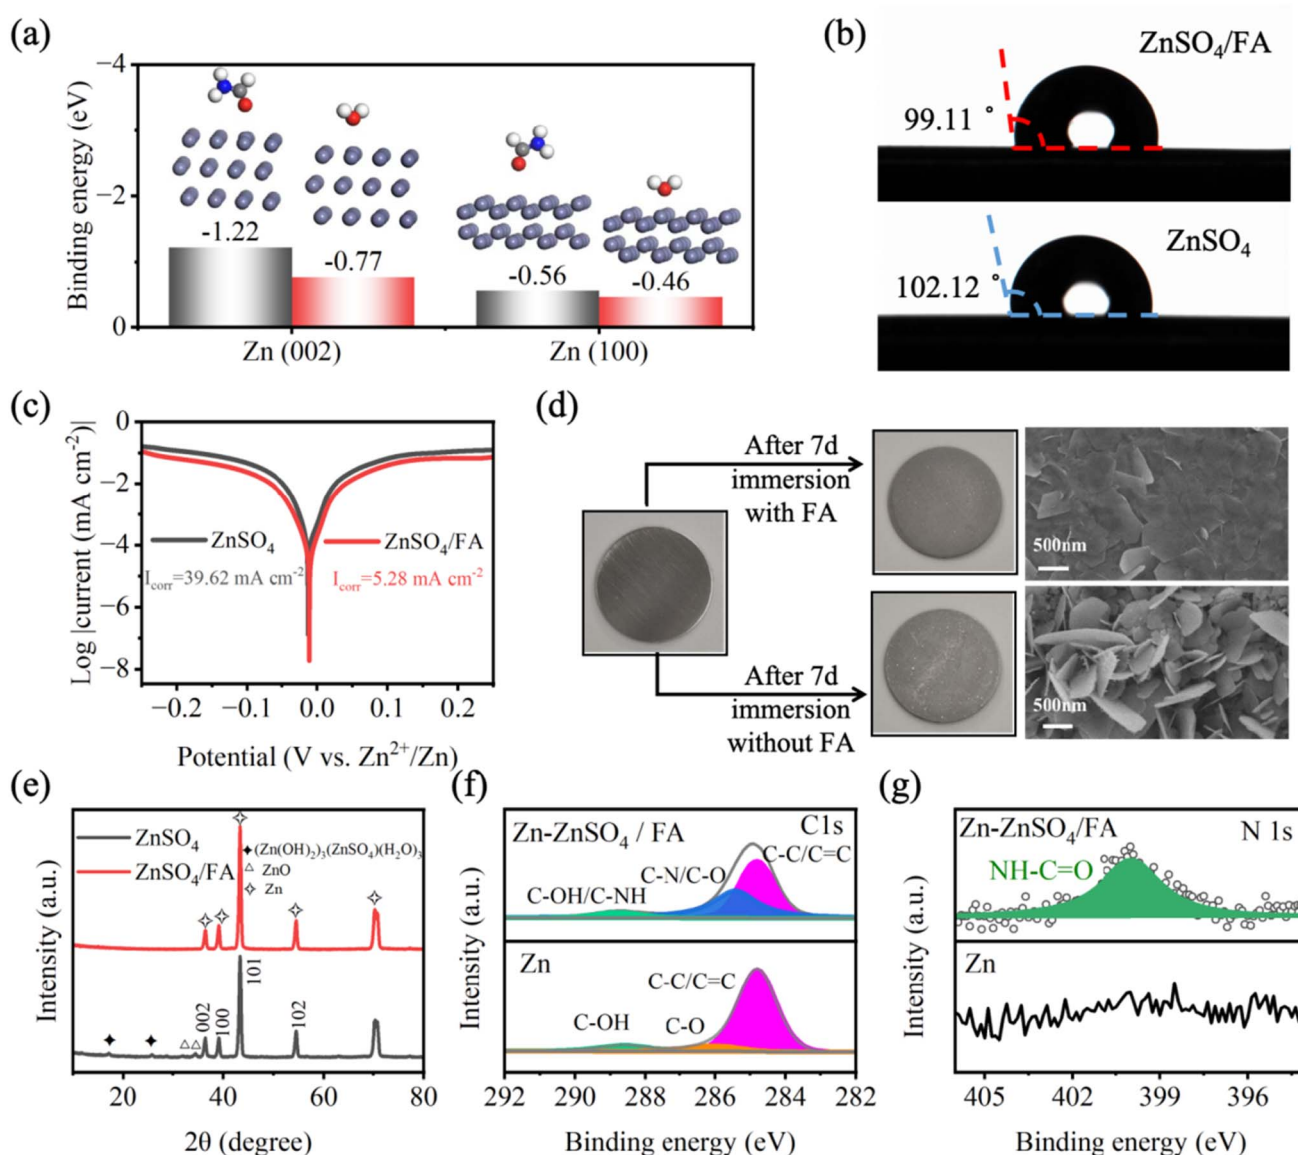


Fig. 2 (a) The adsorption energy of H_2O and FA molecules on Zn (002) and Zn (100) surfaces, respectively. (b) Contact angles of pure ZnSO_4 electrolyte and ZnSO_4/FA electrolyte. (c) Linear polarization curves of the Zn anode in the pure ZnSO_4 electrolyte and ZnSO_4/FA electrolyte. (d) Optical photographs and SEM images of the pristine Zn anode and Zn anode after immersion. (e) XRD patterns of the Zn anode after immersion. XPS spectra of (f) C 1s and (g) N 1s for the Zn foil before and after immersion.

the electrolyte, which is consistent with the calculation of adsorption energy. The effect of the metal–molecule interface on zinc metal corrosion is quantified by a corrosion test (Fig. 2c).^{45–47} Compared with pure ZnSO₄ electrolyte, the Zn anode in ZnSO₄/FA electrolytes has a lower corrosion current density (from 39.62 mA cm⁻² to 5.28 mA cm⁻²), and the corrosion potential is more positive, indicating that the metal–molecule interface enhances the corrosion resistance of the Zn anode in ZnSO₄/FA electrolyte.

Furthermore, self-corrosion tests are carried out to verify the protective effect of the metal–molecule interface during the battery rest by soaking the zinc metal in electrolytes for 7 days. In general, due to the thermodynamic instability of zinc in aqueous solution, self-corrosion occurs spontaneously when the zinc metal is immersed in the aqueous electrolyte, resulting in the loss of the zinc anode and the formation of loose and irregular sheets of corrosion by-products on the surface.⁴⁸ Compared with pure ZnSO₄ electrolyte, the surface of zinc metal immersed in ZnSO₄/FA electrolyte for 7 days is more homogeneous and smoother (Fig. 2d), indicating that the adsorbed FA layer can effectively block the side reactions in aqueous electrolyte, which is also confirmed by XRD results (Fig. 2e). In the XRD pattern of the zinc foil after cycling in the pure ZnSO₄ electrolyte, it can be observed that peaks corresponding to ZnO and (Zn(OH)₂)₃(ZnSO₄)(H₂O)₃ by-products appear in the range of 0° to 35°. However, in the XRD pattern of the zinc foil after cycling in the ZnSO₄/FA electrolyte, no obvious by-product peaks are observed, indicating that the FA additive has an inhibition effect on side reactions. Subsequently, the binding structure between adsorbed FA and the Zn anode is studied by X-ray photoelectron spectroscopy (XPS) (Fig. 2f and g). In the C 1s spectrum of the zinc foil soaked in ZnSO₄/FA electrolyte, a new peak of C–NH appears, which is correlated with the FA additive. Similarly, in the N 1s spectrum, it can be found that there is no peak related to N in the pure ZnSO₄ electrolyte. However, a peak of NH–C=O appears in the ZnSO₄/FA electrolyte, which provides evidence of the adsorption of FA molecules on the surface of zinc metal. In addition, in order to further illustrate the inhibition effect of metal–molecule interface on side reactions, the dynamic measurement of Zn||Zn symmetric batteries is carried out by alternating cycling and resting measurement methods, that is, 30 h of resting after every 30 h of cycling at a current density of 1 mA cm⁻² and a capacity of 0.5 mA h cm⁻². As shown in Fig. S10,[†] the voltage distribution of the Zn||Zn symmetric battery containing pure ZnSO₄ electrolyte shows a serious fluctuation after a 123 h test, while the Zn||Zn symmetric battery containing the FA electrolyte shows stable voltage hysteresis throughout the 900 h test, demonstrating the ability of the metal–molecule interface to stabilize the Zn anode.

3.3 SEI characteristic and homogeneous zinc deposition

The energy levels of the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO) of FA and H₂O molecules are calculated to clarify the redox stability (Fig. S11[†]). It is found that FA has a higher HOMO

energy level and a lower LUMO energy level than H₂O (−5.877 eV vs. −6.748 eV, −0.599 eV vs. 1.061 eV), which means that FA molecules easily gain electrons, and are reduced to SEI before H₂O reduction, thereby inhibiting side reactions on the zinc surface and reducing the production of by-products. In order to obtain more accurate results, zinc was deposited directly on a blank TEM copper grid using ZnSO₄/FA electrolyte, and TEM was performed. As shown in Fig. S12,[†] the lattice fringes of ZnO (002) and ZnS (111) are identified in the SEI layer, which is formed in the first few charge and discharge cycles. In the energy dispersive X-ray spectroscopy (EDS) mapping, it can be observed that N, Zn, O, and S elements are uniformly dispersed on the whole particle surface within the Zn deposits.⁴⁹ In addition, the surface was further investigated by XPS with different sputtering depths. Combined with peak fitting (Fig. 3a–d), it is evidenced that the component at the top surface is primarily composed of organic components, represented by C–O, C=O and C–C. The signal of inorganic components ZnS and ZnO becomes stronger when sputtered to the depth of 10 nm. Additionally, the non-sputtered electrode shows the weakest signal in the Zn 2p spectrum due to the overcoating of the organic component. The analysis indicates that the upper surface of SEI is primarily composed of organic components, while the inner part of SEI is composed of inorganic substances like ZnS and ZnO. The SEI layer not only blocks the contact between the zinc metal and the water and inhibits the side reactions, but also provides the diffusion path of Zn²⁺ and homogenizes the Zn²⁺ flux.⁵⁰ According to previous reports, ZnS and ZnO play an important role in improving the stability and reversibility of zinc anodes.^{51,52} In order to further understand the positive effects of the *in situ* constructed SEI on stabilizing the Zn anode and on regulating deposition behavior, the morphology of deposited Zn and the electrochemical properties of ZnSO₄ and ZnSO₄/FA electrolytes are further explored. Fig. 3e and f are the SEM images of the surface of the zinc foils after one cycle in the two electrolyte system. It can be seen that the surface of the zinc foil using pure ZnSO₄ electrolyte has a typical dendrite morphology, while the surface of the zinc foil using ZnSO₄/FA electrolyte is flat. According to the SEM images of the cross sections of zinc foils after cycling in the two electrolyte system as shown in Fig. 3g and h, the zinc foil with ZnSO₄/FA electrolyte is smooth and dense, while the zinc foil with pure ZnSO₄ electrolyte has obvious protrusions on the surface and disordered and loose deposition. Not surprisingly, the deposition thickness (32 μm) is larger than that in the ZnSO₄/FA electrolyte (28 μm), demonstrating that FA can promote uniform and dense zinc deposition.

CA is an electrochemical method for characterizing changes in the concentration of electroactive substances near a surface. Fig. S13[†] shows the change of current response determined by the nucleation center with time during deposition time of 300 s under −200 mV overpotential. For pure ZnSO₄ electrolyte, the current density reaches its stable value (~−125 mA cm⁻²) shortly after overpotential being applied, suggesting activation of all nucleation sites. In contrast, the activation time of the battery using ZnSO₄/FA electrolyte is

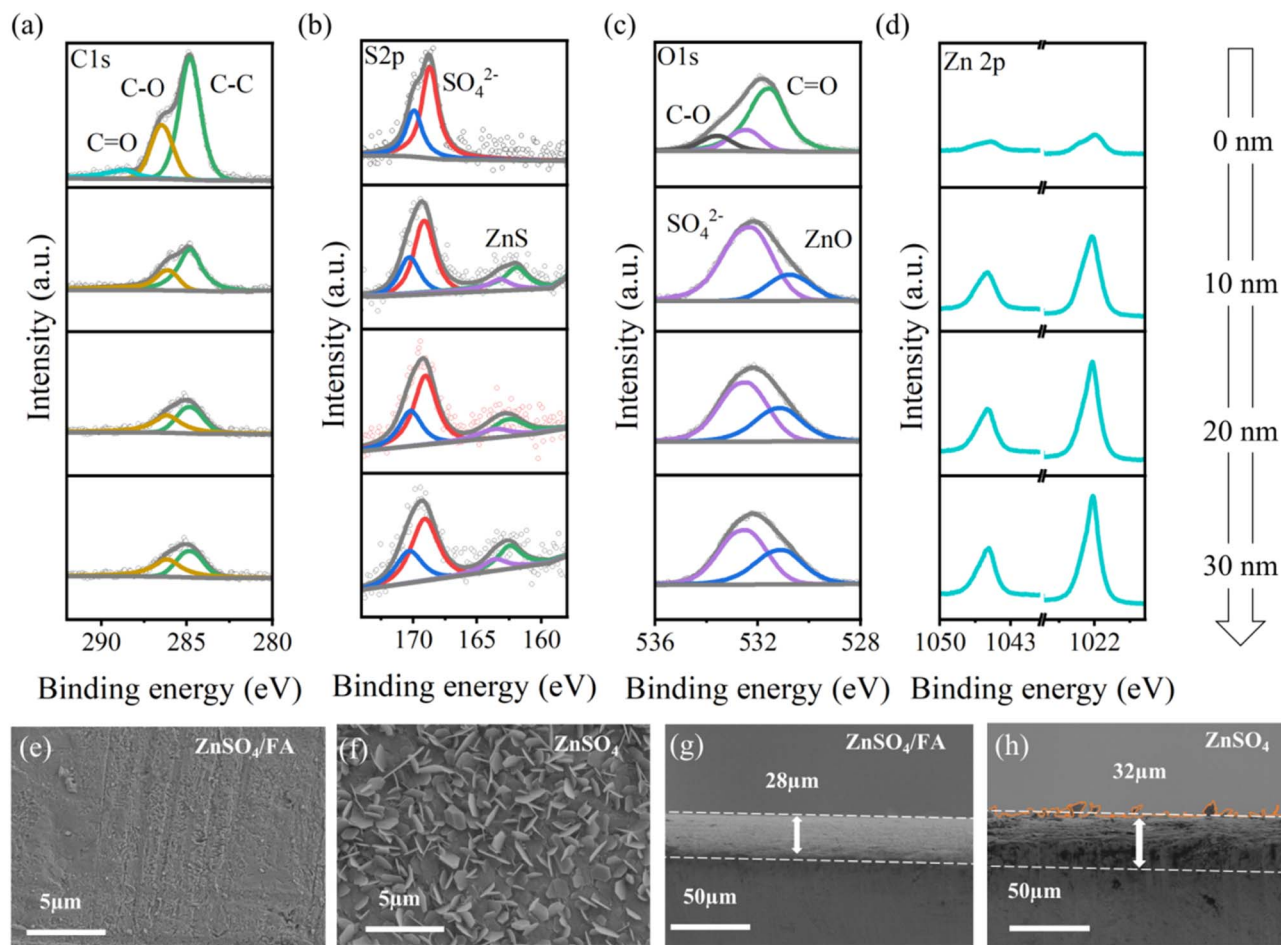


Fig. 3 (a–d) XPS depth profile of the Zn anode after 25 plating/stripping cycles in ZnSO₄/FA electrolyte at a current density of 1 mA cm⁻² with a capacity of 0.5 mA h cm⁻². (e and f) The plan-view and (g and h) cross section SEM images of the Zn anode after a plating/stripping cycle in (e and g) ZnSO₄/FA electrolyte and (f and h) pure ZnSO₄ electrolyte at a current density of 1 mA cm⁻² with a capacity of 0.5 mA h cm⁻².

prolonged, and the current continues to increase slowly and maintains a smaller current value than that of the pure ZnSO₄ electrolyte, which implies that the nucleation sites in the ZnSO₄/FA electrolyte are slowly and gradually exposed, avoiding the rapid uneven growth of zinc nuclei and thus inhibiting the growth of zinc dendrites. The differences in the nucleation mechanism and the stable current density can be attributed to the adsorption of FA molecules on the surface of the Zn anode, thereby reducing the number of nucleation sites in the ZnSO₄/FA electrolyte and slowing down the formation of nuclei. In addition, from the deposition behavior of zinc (Fig. S14[†]), it is suggested that the nucleation and growth overpotential in the ZnSO₄/FA electrolyte are higher than those in pure ZnSO₄ electrolyte. The higher nucleation overpotential usually requires a stronger driving force in the initial nucleation process, thereby depositing fine zinc particles and inhibiting zinc dendrite growth. The XRD pattern of zinc anode cycling for 20 cycles in pure ZnSO₄ electrolyte and ZnSO₄/FA electrolyte (Fig. S15[†]) shows that for the Zn anode cycling in pure ZnSO₄ electrolyte a peak of Zn₄(OH)₆SO₄·xH₂O appears at about 9.8°, indicating that the addition of FA can inhibit the side reactions.

3.4 Highly reversible zinc deposition/stripping behavior

In order to further investigate the effect of FA additive on the stability and reversibility of aqueous zinc-ion batteries, Zn||Zn symmetric batteries and Zn||Cu asymmetric batteries are assembled and tested. According to the galvanostatic charge-discharge (GCD) curve (Fig. 4a), the symmetric battery using ZnSO₄/FA electrolyte exhibits a constant plating/stripping voltage hysteresis of about 50 mV at a current density of 1 mA cm⁻² and a cut-off capacity of 0.5 mA h cm⁻², with stable cycling for more than 1600 hours. The Zn||Zn symmetric battery using pure ZnSO₄ electrolyte experiences a sudden decrease in polarization voltage only after 375 hours of cycling, which may be due to a short circuit caused by dendrite growth. For the Zn||Zn symmetric battery with ZnSO₄/FA electrolyte running at a current density of 2 mA cm⁻², cut-off capacity of 0.5 mA h cm⁻² and current density of 0.5 mA cm⁻², cut-off capacity of 0.25 mA h cm⁻² can stably cycle for 1400 h and 1800 h, respectively, which are much better than those of batteries using pure ZnSO₄ electrolyte under the same conditions (Fig. S16 and S17[†]). As presented in Fig. 4b, in the rate performance of the Zn||Zn symmetric battery, the symmetric



Fig. 4 (a) Cycling performance of Zn||Zn symmetric batteries at 1 mA cm^{-2} and 0.5 mA h cm^{-2} . (b) Rate performance of the Zn||Zn symmetric batteries. (c) Variable temperature performance of Zn||Zn symmetric batteries in the temperature range from $30 \text{ }^\circ\text{C}$ to $-30 \text{ }^\circ\text{C}$. (d) The coulombic efficiency (CE) of the Zn||Cu asymmetric batteries at 1 mA cm^{-2} and 0.5 mA h cm^{-2} . The corresponding voltage–capacity curves for the selected cycles in (e) ZnSO₄/FA electrolyte and (f) pure ZnSO₄ electrolyte.

battery using pure ZnSO₄ electrolyte has a short circuit in the cycle at the current density of 15 mA cm^{-2} , while the symmetric battery using ZnSO₄/FA electrolyte has a stable performance, showing smooth voltage distribution and small voltage hysteresis at different current densities. The detailed results of voltage hysteresis are shown in Table S1.† This excellent stability is mainly attributed to the improved transport dynamics of Zn²⁺ by the FA-derived SEI. The low temperature characteristics of ZnSO₄/FA electrolyte are also verified. Fig. 4c shows the performance of Zn||Zn symmetric batteries at varying temperatures. Zn||Zn symmetric batteries using ZnSO₄/FA electrolyte in the temperature range from $30 \text{ }^\circ\text{C}$ to $-30 \text{ }^\circ\text{C}$ exhibit a smooth voltage distribution and small voltage hysteresis. However, in the pure ZnSO₄ electrolyte, a short circuit occurs at $-10 \text{ }^\circ\text{C}$. These results demonstrate that a much better low temperature performance is achieved with using ZnSO₄/FA electrolyte as compared with pure ZnSO₄ electrolyte. The Zn||Zn symmetric battery using ZnSO₄/FA electrolyte was then tested at a low temperature of $-20 \text{ }^\circ\text{C}$ at 1 mA cm^{-2} and 0.5 mA h cm^{-2} , as shown in Fig. S18.† It can be

seen that the Zn||Zn symmetric battery can cycle stably for more than 1800 h at a low temperature of $-20 \text{ }^\circ\text{C}$, which further proves the good low-temperature performance of the ZnSO₄/FA electrolyte. The improved low-temperature performance of the ZnSO₄/FA electrolyte is attributed to the disruption of the original hydrogen bonding network in the electrolyte. The results of binding energy calculation, and the alteration in the type of hydrogen bonding as indicated in the infrared spectra, demonstrate that the addition of FA breaks the original hydrogen bonding network. This leads to a reduction in the proportion of strong hydrogen bonds between H₂O molecules, and an increase in the proportion of weak hydrogen bonds between FA and H₂O. The freezing process involves a complex rearrangement of disordered water molecules into ordered ice. This rearrangement is driven by forming extra hydrogen bonds (H-bonds). It is a process in which the hydrogen bond changes from disorder to order. Consequently, the breaking of the hydrogen bonding network reduces the degree of order, resulting in a lower freezing point and thus better low-temperature properties.

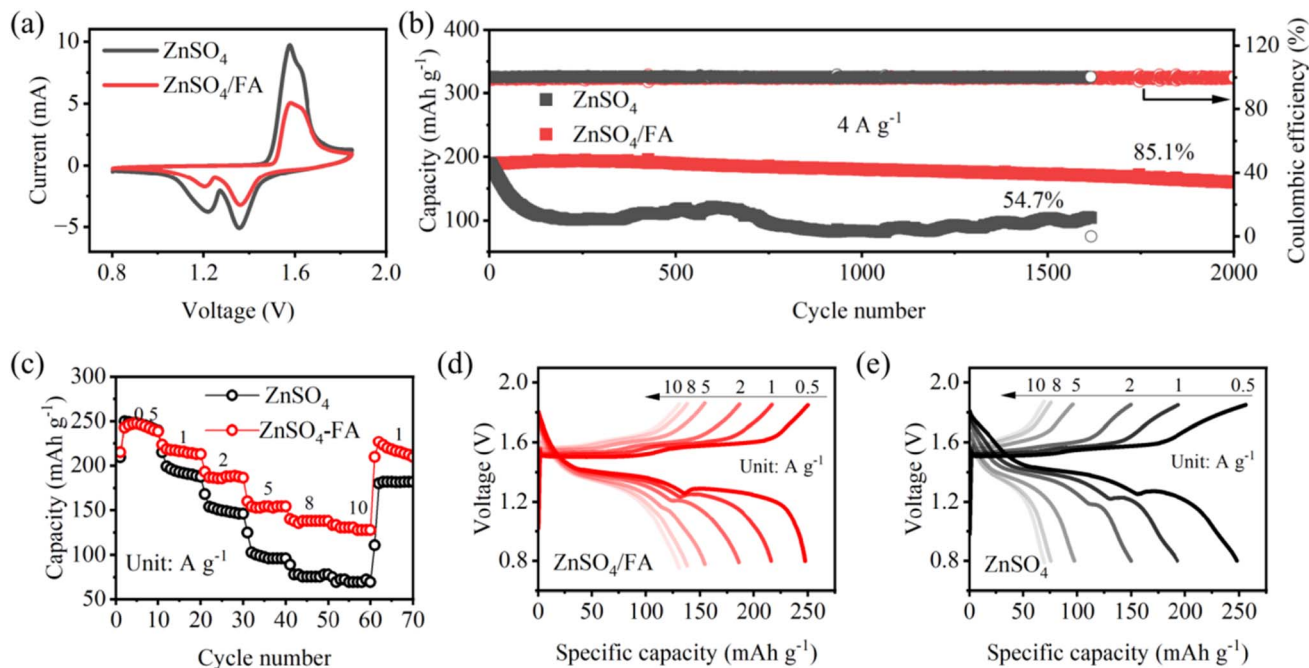


Fig. 5 (a) The CV curves of the Zn||MnO₂ full cells in pure ZnSO₄ electrolyte and ZnSO₄/FA electrolyte. (b) The long-term cycling performance of the Zn||MnO₂ full cells in pure ZnSO₄ electrolyte and ZnSO₄/FA electrolyte. (c) The rate performance of the Zn||MnO₂ full cells in pure ZnSO₄ electrolyte and ZnSO₄/FA electrolyte and the corresponding charge–discharge profiles. Charging/discharging curves of Zn||MnO₂ full cells at different current densities in (d) ZnSO₄/FA and (e) ZnSO₄ electrolyte.

In addition, the reversible zinc behavior of Zn||Cu asymmetric batteries is investigated at the current density of 1 mA cm⁻² and a cutoff capacity of 0.5 mA h cm⁻² (Fig. 4d–f). The Zn||Cu asymmetric battery using ZnSO₄/FA electrolyte has a high initial coulombic efficiency of 93.71%, stable operation for more than 1700 hours, and an average coulombic efficiency of 99.24%, much better than cycling in pure ZnSO₄ electrolyte (98.28% for 292 cycles). Additionally, the overpotential for the selected cycles of Zn||Cu asymmetric batteries using ZnSO₄/FA electrolyte is about 2.9 mV, which is lower than that of Zn||Cu asymmetric batteries using pure ZnSO₄ electrolyte (10.6 mV), and the voltage curve is more consistent, indicating that the Zn||Cu asymmetric batteries using ZnSO₄/FA electrolyte have better reversibility during the process of Zn stripping/plating at the electrode/electrolyte interface.

3.5 Performance of Zn||MnO₂ full cells

As a proof-of-concept, MnO₂ is chosen as the cathode material for full cell assembly to verify the practicality of our strategy. Both CV curves show similar redox peaks (Fig. 5a), indicating that FA plays a negligible role in electrochemical redox processes. Meanwhile, the reduction of the redox peak in the CV curve for ZnSO₄/FA may be due to the strong interaction between FA and Zn²⁺ and sluggish interfacial Zn²⁺ charge transfer kinetics.³³ The Zn||MnO₂ full cells are tested for long cycle and rate performance. As shown in Fig. 5b, Zn||MnO₂ full cells with ZnSO₄/FA electrolyte exhibit better long-cycle performance and maintain a discharge capacity of 160.5 mA h g⁻¹ after 2000 cycles at a current density of 4 A g⁻¹, with a capacity retention of 85.1%. Under the same cycling conditions, pure

ZnSO₄ electrolyte-based cells show significantly reduced capacity, and the retention rate is only 54.7% after 1616 cycles. Furthermore, the rate performance of the Zn||MnO₂ full cell is studied and shown in Fig. 5c–e. The Zn||MnO₂ full cell using ZnSO₄ electrolyte exhibits greater capacity decay as the current increases, and an irreversible capacity decay occurs when the current density returns to 1 A g⁻¹ (89.6% capacity retention compared to the average capacity of the 10 cycles at 1 A g⁻¹). In contrast, the Zn||MnO₂ full cell using ZnSO₄/FA electrolyte offers higher capacities at different current densities, and provides a superior capacity retention rate of 99.8% when current density returns to 1 A g⁻¹, indicating that the reversibility of the Zn anode is improved by using FA electrolyte additive.

4. Conclusions

In this work, formamide (FA) is introduced as an electrolyte additive to ZnSO₄ aqueous electrolyte for the first time. Firstly, the addition of FA changes the solvation structure of Zn²⁺ and reduces the number of H₂O molecules in the solvation structure. Moreover, FA interacts with the free H₂O molecules to break the original hydrogen-bonding network, which radically reduces the activity of H₂O molecules, inhibits the side reactions related to H₂O molecules and improves the low temperature performance of the battery significantly. In addition, FA is found to be a good interfacial stabilizer. This is mainly due to the fact that FA has zinc affinity and prevents H₂O from contacting the Zn anode surface by adsorbing on the surface of the Zn anode, forming a water-poor EDL structure, thus inhibiting

side reactions at the interface. In the first cycle, the protective effect of adsorbed FA is dominant due to the incomplete formation of the SEI. With the charge–discharge cycles proceeding, the Zn surface will be completely covered by FA reduction products, and the dominant role of uniform zinc deposition is generated by the SEI. Benefiting from these positive effects, the Zn||Zn symmetric battery using ZnSO₄/FA electrolyte exhibits a constant plating/stripping voltage hysteresis of about 50 mV at a current density of 1 mA cm⁻² and a cut-off capacity of 0.5 mA h cm⁻², with stable cycling for more than 1600 hours. The Zn||Cu asymmetric battery using ZnSO₄/FA electrolyte has a high initial coulombic efficiency of 93.71% and stable operation for more than 1700 hours with an average coulombic efficiency of 99.24%. Additionally, the Zn||MnO₂ full batteries using ZnSO₄/FA electrolyte have achieved excellent cycling performance with a capacity retention rate of 85.1% for more than 2000 cycles at a current density of 4 A g⁻¹, demonstrating the great potential of the ZnSO₄/FA electrolyte additive for future high-performance aqueous zinc-ion batteries.

Author contributions

Xiaomin Li: conceptualization, methodology, investigation, formal analysis, data curation, writing – original draft, writing – review & editing. Jinwei Miao: formal analysis, methodology. Fulong Hu: formal analysis, writing – original draft, methodology. Kang Yan: formal analysis, methodology. Lin Song: writing – review & editing. Huiqing Fan: writing – review & editing. Longtao Ma: writing – review & editing. Weijia Wang: writing – review & editing, resources, supervision.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

Xiaomin Li and Jinwei Miao contributed equally to this work. This study was sponsored by the National Natural Science Foundation of China (52272124), the Fundamental Research Funds for the Central Universities (D5000230071), and the Practice and Innovation Funds for Graduate Students of Northwestern Polytechnical University (PF2023150). This research performed SEM, TEM, XRD, Raman, and XPS tests in the Analytical & Testing Center of Northwestern Polytechnical University.

References

- 1 D. Wang, Q. Li, Y. Zhao, H. Hong, H. Li, Z. Huang, G. Liang, Q. Yang and C. Zhi, *Adv. Energy Mater.*, 2022, **12**, 2102707.
- 2 W. Chen, G. Li, A. Pei, Y. Li, L. Liao, H. Wang, J. Wan, Z. Liang, G. Chen, H. Zhang, J. Wang and Y. Cui, *Nat. Energy*, 2018, **3**, 428–435.
- 3 J. Yan, E. H. Ang, Y. Yang, Y. Zhang, M. Ye, W. Du and C. C. Li, *Adv. Funct. Mater.*, 2021, **31**, 2010213.
- 4 J. Shi, T. Sun, J. Bao, S. Zheng, H. Du, L. Li, X. Yuan, T. Ma and Z. Tao, *Adv. Funct. Mater.*, 2021, **31**, 2102035.
- 5 J. Zhao, J. Zhang, W. Yang, B. Chen, Z. Zhao, H. Qiu, S. Dong, X. Zhou, G. Cui and L. Chen, *Nano Energy*, 2019, **57**, 625–634.
- 6 J. Yang, H. Yan, H. Hao, Y. Song, Y. Li, Q. Liu and A. Tang, *ACS Energy Lett.*, 2022, **7**, 2331–2339.
- 7 L. Ma, M. A. Schroeder, O. Borodin, T. P. Pollard, M. S. Ding, C. Wang and K. Xu, *Nat. Energy*, 2020, **5**, 743–749.
- 8 Y. Zhang, Z. Cao, S. Liu, Z. Du, Y. Cui, J. Gu, Y. Shi, B. Li and S. Yang, *Adv. Energy Mater.*, 2022, **12**, 2103979.
- 9 Z. Hou, Y. Gao, R. Zhou and B. Zhang, *Adv. Funct. Mater.*, 2022, **32**, 2107584.
- 10 Y. Lv, M. Zhao, Y. Du, Y. Kang, Y. Xiao and S. Chen, *Energy Environ. Sci.*, 2022, **15**, 4748–4760.
- 11 Y. Liu, Y. An, L. Wu, J. Sun, F. Xiong, H. Tang, S. Chen, Y. Guo, L. Zhang, Q. An and L. Mai, *ACS Nano*, 2023, **17**, 552–560.
- 12 S. H. Park, S. Y. Byeon, J.-H. Park and C. Kim, *ACS Energy Lett.*, 2021, **6**, 3078–3085.
- 13 Y. Yang, H. Yang, R. Zhu and H. Zhou, *Energy Environ. Sci.*, 2023, **16**, 2723–2731.
- 14 S. Liu, J. Mao, W. K. Pang, J. Vongsvivut, X. Zeng, L. Thomsen, Y. Wang, J. Liu, D. Li and Z. Guo, *Adv. Funct. Mater.*, 2021, **31**, 2104281.
- 15 J. Zhu, Z. Bie, X. Cai, Z. Jiao, Z. Wang, J. Tao, W. Song and H. J. Fan, *Adv. Mater.*, 2022, **34**, 2207209.
- 16 J. Zhou, F. Wu, Y. Mei, Y. Hao, L. Li, M. Xie and R. Chen, *Adv. Mater.*, 2022, **34**, 2200782.
- 17 Q. Zhang, Y. Su, Z. Shi, X. Yang and J. Sun, *Small*, 2022, **18**, 2203583.
- 18 Y. Mu, Z. Li, B.-k. Wu, H. Huang, F. Wu, Y. Chu, L. Zou, M. Yang, J. He, L. Ye, M. Han, T. Zhao and L. Zeng, *Nat. Commun.*, 2023, **14**, 4205.
- 19 C. Zhu, P. Li, G. Xu, H. Cheng and G. Gao, *Coord. Chem. Rev.*, 2023, **485**, 215142.
- 20 Y. Song, P. Ruan, C. Mao, Y. Chang, L. Wang, L. Dai, P. Zhou, B. Lu, J. Zhou and Z. He, *Nano-Micro Lett.*, 2022, **14**, 218.
- 21 L. Cao, D. Li, F. A. Soto, V. Ponce, B. Zhang, L. Ma, T. Deng, J. M. Seminario, E. Hu, X.-Q. Yang, P. B. Balbuena and C. Wang, *Angew. Chem., Int. Ed.*, 2021, **60**, 18845–18851.
- 22 C. Nie, G. Wang, D. Wang, M. Wang, X. Gao, Z. Bai, N. Wang, J. Yang, Z. Xing and S. Dou, *Adv. Energy Mater.*, 2023, **13**, 2300606.
- 23 J. Li, Z. Guo, J. Wu, Z. Zheng, Z. Yu, F. She, L. Lai, H. Li, Y. Chen and L. Wei, *Adv. Energy Mater.*, 2023, 2301743.
- 24 Y. Geng, L. Pan, Z. Peng, Z. Sun, H. Lin, C. Mao, L. Wang, L. Dai, H. Liu, K. Pan, X. Wu, Q. Zhang and Z. He, *Energy Storage Mater.*, 2022, **51**, 733–755.
- 25 T. Zhang, Y. Tang, S. Guo, X. Cao, A. Pan, G. Fang, J. Zhou and S. Liang, *Energy Environ. Sci.*, 2020, **13**, 4625–4665.
- 26 G. Gao, G. Li, Y. Zhao, L. Ma and W. Huang, *Matter*, 2023, **6**, 3732–3746.
- 27 C. Han, W. Li, H. K. Liu, S. Dou and J. Wang, *Nano Energy*, 2020, **74**, 104880.
- 28 R. Qin, Y. Wang, M. Zhang, Y. Wang, S. Ding, A. Song, H. Yi, L. Yang, Y. Song, Y. Cui, J. Liu, Z. Wang, S. Li, Q. Zhao and F. Pan, *Nano Energy*, 2021, **80**, 105478.

- 29 S. Guo, L. Qin, T. Zhang, M. Zhou, J. Zhou, G. Fang and S. Liang, *Energy Storage Mater.*, 2021, **34**, 545–562.
- 30 X. Li, X. Wang, L. Ma and W. Huang, *Adv. Energy Mater.*, 2022, **12**, 2202068.
- 31 F. Wang, O. Borodin, M. S. Ding, M. Gobet, J. Vatamanu, X. Fan, T. Gao, N. Eidson, Y. Liang, W. Sun, S. Greenbaum, K. Xu and C. Wang, *Joule*, 2018, **2**, 927–937.
- 32 N. Chang, T. Li, R. Li, S. Wang, Y. Yin, H. Zhang and X. Li, *Energy Environ. Sci.*, 2020, **13**, 3527–3535.
- 33 L. Cao, D. Li, E. Hu, J. Xu, T. Deng, L. Ma, Y. Wang, X.-Q. Yang and C. Wang, *J. Am. Chem. Soc.*, 2020, **142**, 21404–21409.
- 34 S. Liu, J. Mao, W. K. Pang, J. Vongsvivut, X. Zeng, L. Thomsen, Y. Wang, J. Liu, D. Li and Z. Guo, *Adv. Funct. Mater.*, 2021, **31**, 2104281.
- 35 Z. Huang, T. Wang, X. Li, H. Cui, G. Liang, Q. Yang, Z. Chen, A. Chen, Y. Guo, J. Fan and C. Zhi, *Adv. Mater.*, 2021, **34**, e2106180.
- 36 Y. Jin, L. Zou, L. Liu, M. H. Engelhard, R. L. Patel, Z. Nie, K. S. Han, Y. Shao, C. Wang, J. Zhu, H. Pan and J. Liu, *Adv. Mater.*, 2019, **31**, 1900567.
- 37 K. Wang, F. Liu, Q. Li, J. Zhu, T. Qiu, X.-X. Liu and X. Sun, *Chem. Eng. J.*, 2023, **452**, 139577.
- 38 L. Zhou, F. Wang, F. Yang, X. Liu, Y. Yu, D. Zheng and X. Lu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202208051.
- 39 W. W. Rudolph and C. C. Pye, *Phys. Chem. Chem. Phys.*, 1999, **1**, 4583–4593.
- 40 A. C. Hayes, P. Kruus and W. A. Adams, *J. Solution Chem.*, 1984, **13**, 61–75.
- 41 W. W. Rudolph, M. H. Brooker and P. R. Tremaine, *J. Solution Chem.*, 1999, **28**, 621–630.
- 42 Q. Zhang, Y. Ma, Y. Lu, L. Li, F. Wan, K. Zhang and J. Chen, *Nat. Commun.*, 2020, **11**, 4463.
- 43 L. Miao, R. Wang, S. Di, Z. Qian, L. Zhang, W. Xin, M. Liu, Z. Zhu, S. Chu, Y. Du and N. Zhang, *ACS Nano*, 2022, **16**, 9667–9678.
- 44 Y. Liu, X. Tao, Y. Wang, C. Jiang, C. Ma, O. Sheng, G. Lu and X. W. Lou, *Science*, 2022, **375**, 739–745.
- 45 M. Yan, C. Xu, Y. Sun, H. Pan and H. Li, *Nano Energy*, 2021, **82**, 105739.
- 46 X. Xie, S. Liang, J. Gao, S. Guo, J. Guo, C. Wang, G. Xu, X. Wu, G. Chen and J. Zhou, *Energy Environ. Sci.*, 2020, **13**, 503–510.
- 47 Y. Jin, K. S. Han, Y. Shao, M. L. Sushko, J. Xiao, H. Pan and J. Liu, *Adv. Funct. Mater.*, 2020, **30**, 2003932.
- 48 R. Sun, D. Han, C. Cui, Z. Han, X. Guo, B. Zhang, Y. Guo, Y. Liu, Z. Weng and Q.-H. Yang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202303557.
- 49 M. Chen, J. Zheng, Y. Liu, O. Sheng, Z. Ju, G. Lu, T. Liu, Y. Wang, J. Nai, Q. Wang and X. Tao, *Adv. Funct. Mater.*, 2021, **31**, 2102228.
- 50 C. Huang, X. Zhao, S. Liu, Y. Hao, Q. Tang, A. Hu, Z. Liu and X. Chen, *Adv. Mater.*, 2021, **33**, 2100445.
- 51 X. Wang, K. Feng, B. Sang, G. Li, Z. Zhang, G. Zhou, B. Xi, X. An and S. Xiong, *Adv. Energy Mater.*, 2023, 2301670.
- 52 J. Feng, D. Ma, K. Ouyang, M. Yang, Y. Wang, J. Qiu, T. Chen, J. Zhao, B. Yong, Y. Xie, H. Mi, L. Sun, C. He and P. Zhang, *Adv. Funct. Mater.*, 2022, **32**, 2207909.