


Journal of Materials Chemistry A

Materials for energy and sustainability

www.rsc.org/MaterialsA

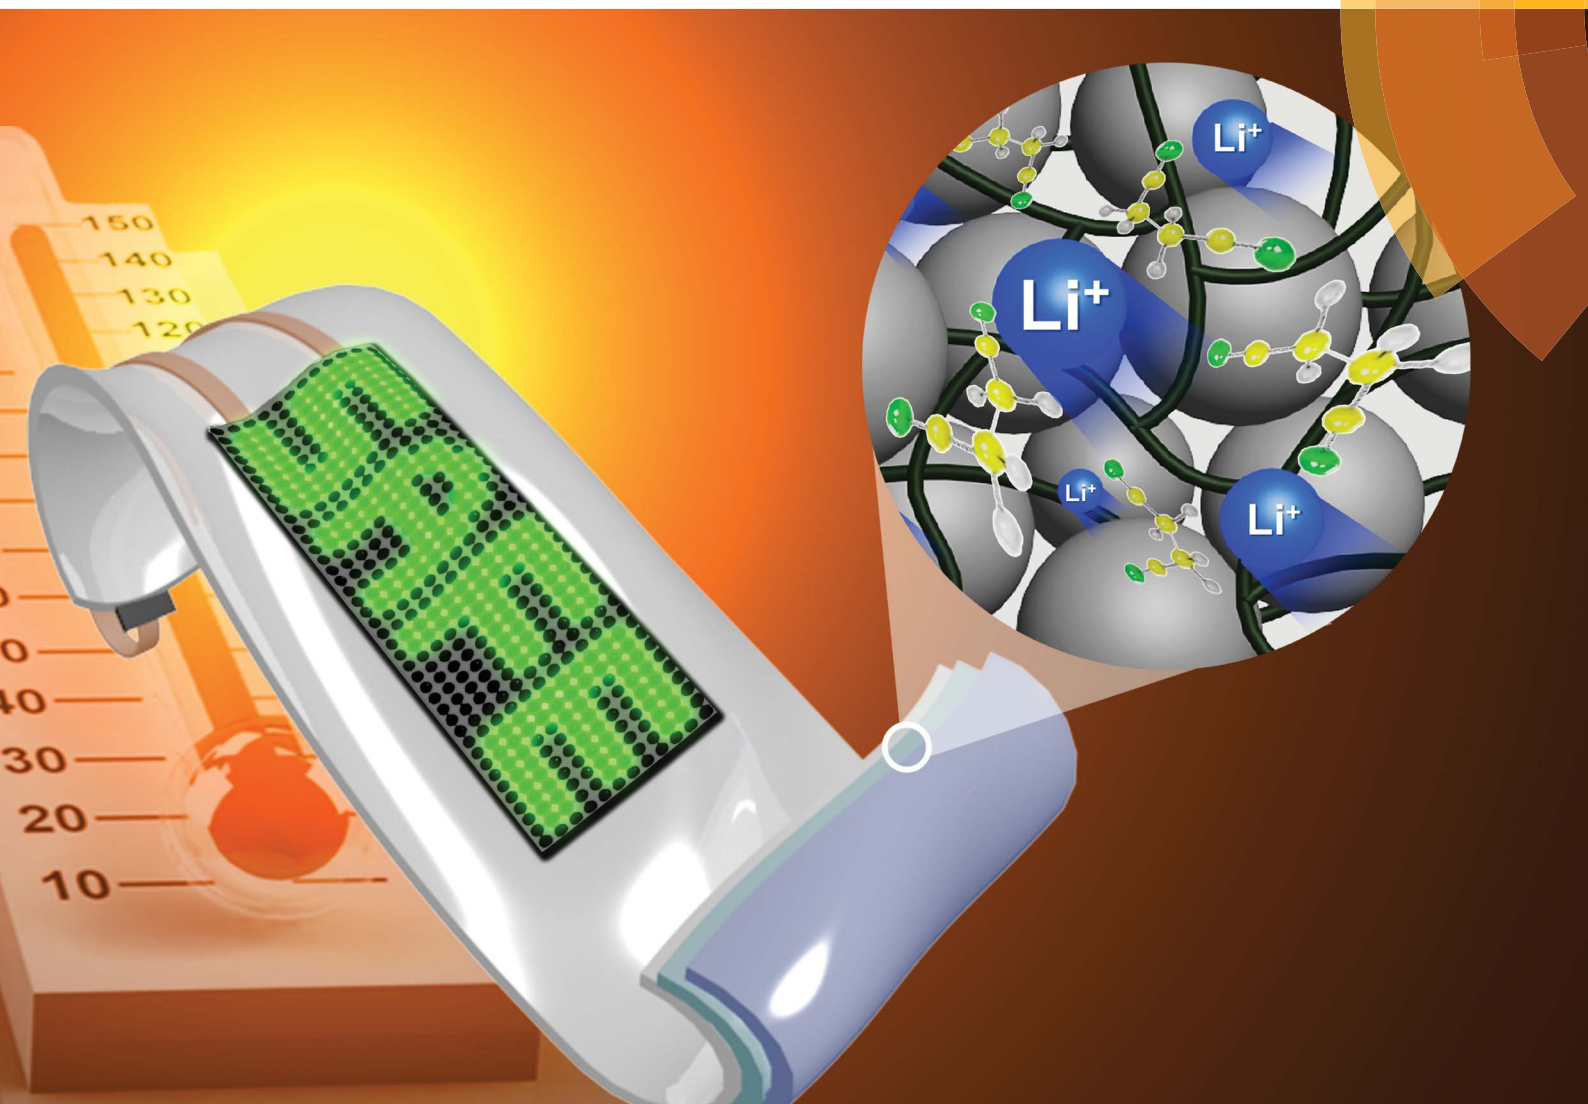

Themed issue: Flexible Energy Storage and Conversion

ISSN 2050-7488



PAPER

Sang-Young Lee *et al.*

A shape-deformable and thermally stable solid-state electrolyte based on a plastic crystal composite polymer electrolyte for flexible/safer lithium-ion batteries

Cite this: *J. Mater. Chem. A*, 2014, 2, 10854

A shape-deformable and thermally stable solid-state electrolyte based on a plastic crystal composite polymer electrolyte for flexible/safer lithium-ion batteries†

Se-Hee Kim,^a Keun-Ho Choi,^a Sung-Ju Cho,^a Joo-Sung Park,^a Kuk Young Cho,^b Chang Kee Lee,^c Sang Bong Lee,^c Jin Kie Shim^c and Sang-Young Lee^{*a}

A solid-state electrolyte with reliable electrochemical performance, mechanical robustness and safety features is strongly pursued to facilitate the progress of flexible batteries. Here, we demonstrate a shape-deformable and thermally stable plastic crystal composite polymer electrolyte (denoted as "PC-CPE") as a new class of solid-state electrolyte to achieve this challenging goal. The PC-CPE is composed of UV (ultraviolet)-cured ethoxylated trimethylolpropane triacrylate (ETPTA) macromer/close-packed Al₂O₃ nanoparticles (acting as the mechanical framework) and succinonitrile-mediated plastic crystal electrolyte (serving as the ionic transport channel). This chemical/structural uniqueness of the PC-CPE brings remarkable improvement in mechanical flexibility and thermal stability, as compared to conventional carbonate-based liquid electrolytes that are fluidic and volatile. In addition, the PC-CPE precursor mixture (*i.e.*, prior to UV irradiation) with well-adjusted rheological properties, *via* collaboration with a UV-assisted imprint lithography technique, produces the micropatterned PC-CPE with tunable dimensions. Notably, the cell incorporating the self-standing PC-CPE, which acts as a thermally stable electrolyte and also a separator membrane, maintains stable charge/discharge behavior even after exposure to thermal shock condition (=130 °C/0.5 h), while a control cell assembled with a carbonate-based liquid electrolyte and a polyethylene separator membrane loses electrochemical activity.

Received 28th January 2014
Accepted 5th March 2014

DOI: 10.1039/c4ta00494a

www.rsc.org/MaterialsA

Introduction

Wearable electronic devices such as bendable smart phones, roll-up displays and patchable/implantable sensors have recently garnered a great deal of attention due to their aesthetic versatility/mobile usability that lies far beyond those accessible with conventional approaches.^{1–5} Lithium-ion rechargeable batteries (hereinafter, referred to as "batteries"), the most widespread portable energy storage system, are recommended as a promising power source to fulfill stringent requirements for wearable electronics. To date, most research activities on flexible batteries have focused on design and fabrication of new functional electrodes, including nanostructured electrode active materials,

low-dimensional carbon nanotubes/graphene-based electrodes and non-metallic current collectors adopting conductive paper/textiles.^{6–14}

In comparison, little attention has been devoted to developing advanced electrolytes for flexible batteries. Currently commercially available liquid electrolytes ensure good electrochemical performance and benign interfacial contact with electrodes, however, their fluidic attributes cause critical limitation in battery design because separator membranes and packaging canisters with fixed dimension are essentially needed for cell assembly. In addition, the potential leakage problem of liquid electrolytes is another thorny issue that impairs electrochemical performance and also safety of cells. As a result, the use of liquid electrolytes poses a big obstacle to the realization of flexible/safe batteries with shape diversity.^{15–17} These challenges arising from the use of liquid electrolytes strongly push us to search for alternative solid-state electrolytes with full-fledged characteristics suitable for flexible battery applications.


Recently, our group reported the bendable and shape-conformable composite gel polymer electrolyte consisting of a UV-crosslinked polymer, carbonate-based liquid electrolyte and nanoparticles.^{18,19} The composite gel polymer

^aInterdisciplinary School of Green Energy, Ulsan National Institute of Science and Technology (UNIST), Ulsan, 689-798, Korea. E-mail: syleek@unist.ac.kr; Fax: +82-52-217-2019; Tel: +82-52-217-2948

^bDivision of Advanced Materials Engineering, Kongju National University, Chungnam, 331-717, Korea

^cKorea Packaging Center, Korea Institute of Industrial Technology, Bucheon, Gyeonggi-do, 421-742, Korea

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c4ta00494a




particular focus on cell performance under thermal shock condition (=130 °C/0.5 h).

The PC-CPE, due to the presence of thermally stable PCE (providing ion transport channels) and also an elaborately structured ETPTA/Al₂O₃ composite (acting as the mechanical framework), shows significant improvement in mechanical flexibility and high-temperature stability. Meanwhile, the PC-CPE precursor mixture (*i.e.*, prior to UV curing) with well-tailored rheological properties, through collaboration with the UV-assisted imprint lithography (UV-IL) technique,^{18,25} produces the micropatterned PC-CPE with tunable dimensions. Based on the structural and physicochemical characterization of the PC-CPE, its feasibility as a new solid-state electrolyte for flexible/safer batteries is explored by scrutinizing the charge/discharge behavior of cells, with a

Fabrication of the plastic crystal composite polymer electrolyte (PC-CPE)

SN, LiTFSI, ETPTA, and 2-hydroxy-2-methyl-1-phenyl-1-prop-
anone (HMPP, photo-initiator) were purchased from Aldrich
and Al_2O_3 nanoparticles (average powder size ~ 300 nm) were
obtained from Sumitomo Chemical. The PCE was prepared by
adding 1 M LiTFSI into SN melted at 60°C .^{20,21} The weight-
based composition ratio of the PC-CPE precursor mixture was
(ETPTA/PCE = 15/85 w/w)/ Al_2O_3 = 34/66 w/w, wherein the
concentration of HMPP was fixed at 1.0 wt% of ETPTA. The
precursor mixture was subjected to bead-milling for 0.5 h, in
order to attain a uniform dispersion of Al_2O_3 nanoparticles.
Subsequently, the precursor mixture was cast onto a poly-
ethylene terephthalate (PET) sheet and then exposed to UV
irradiation for 20 s, leading to the self-standing PC-CPE film.
The UV curing was performed using a Hg UV-lamp (Lichtzen),
with an irradiation peak intensity of approximately 2000 mW cm^{-2}
on the sample surface. The thickness of the resulting PC-
CPE film was approximately $110\text{ }\mu\text{m}$. PDMS stamps with
microscale maze-patterns were obtained by thermally curing a
commercially available liquid prepolymer mixture composed
of a silicon elastomer base and a curing agent (Sylgard 184,
Dow Corning) on a photoresist master at 80°C for 5 h.¹⁸ A
schematic representation depicting the UV curing-assisted
fabrication process, along with chemical structures and
photographs depicting the mechanical bendability of the
PC-CPE, is provided in Scheme 1.

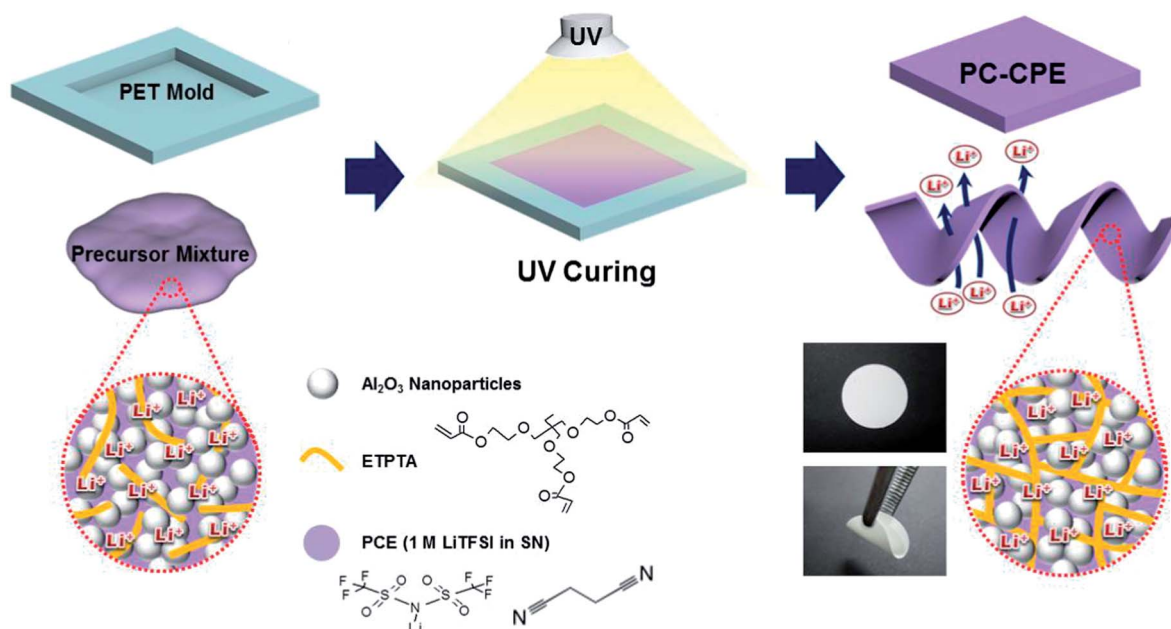

Scheme 1 A schematic representation of the UV curing-assisted fabrication process for PC-CPE, wherein chemical structures and photographs depicting mechanical bendability of PC-CPE are also provided.

Characterization of the microstructure, physical properties and electrochemical performance of the plastic crystal composite polymer electrolyte (PC-CPE)

The thermal characteristics of the PC-CPE, particularly focusing on plastic crystal behavior of SN in the PC-CPE, were evaluated by differential scanning calorimetry (DSC, DuPont Q2000) at a heating rate of $20\text{ }^{\circ}\text{C min}^{-1}$. The UV curing reaction of the PC-CPE was examined using a FT-IR spectrometer (FT-3000, Excalibur) with a spectral resolution of 4 cm^{-1} . The morphology (in particular, dispersion state of Al_2O_3 nanoparticles) of the PC-CPE was investigated using a field emission scanning electron microscope (FE-SEM, S-4800, Hitachi). The mechanical bendability of the PC-CPE was estimated *via* a bending test using a universal tensile tester (LR 10K, Lloyd), where samples were subjected to repeated bending cycle (under longitudinal strain ranging from 10 to 30 mm) at a strain rate of 10 mm min^{-1} , where the number of bending cycles before breakdown of the samples represents their bendability.^{19,23,24} In addition, the mechanical deformability of the PC-CPE was further

characterized after being wound around cylindrical glass rods (diameter = 2.5 and 5.0 mm). The maze-patterned PC-CPE was characterized with an optical microscope (BX41, Olympus), in addition to FE-SEM measurement. The viscosity of the PC-CPE precursor mixture was measured with a viscometer (Haake MARS 3, Thermo Electron GmbH). A conventional carbonate-based liquid electrolyte (here, 1 M LiPF_6 in ethylene carbonate (EC)/dimethyl carbonate (DMC) = 1/1 v/v) was chosen as a control sample of the PC-CPE. The electrochemical stability window of the PC-CPE was measured by linear sweep voltammetry (LSV) performed on a working electrode of stainless-steel and a counter and reference electrode of lithium metal at a scan rate of 1.0 mV s^{-1} . The ionic conductivity of the PC-CPE was obtained using an impedance analyzer (VSP classic, Bio-Logic) over a frequency range of 1 to 10^6 Hz under a temperature range of 30 to $70\text{ }^{\circ}\text{C}$. To evaluate cell performance, a unit cell (2032 coin) was assembled by sandwiching the self-standing PC-CPE between the PCE-soaked LiCoO_2 cathode (LiCoO_2 (average particle size (D_{50}) = $10\text{ }\mu\text{m}$)/PVdF binder/Super-P = 95/3/2 w/w/w) and the

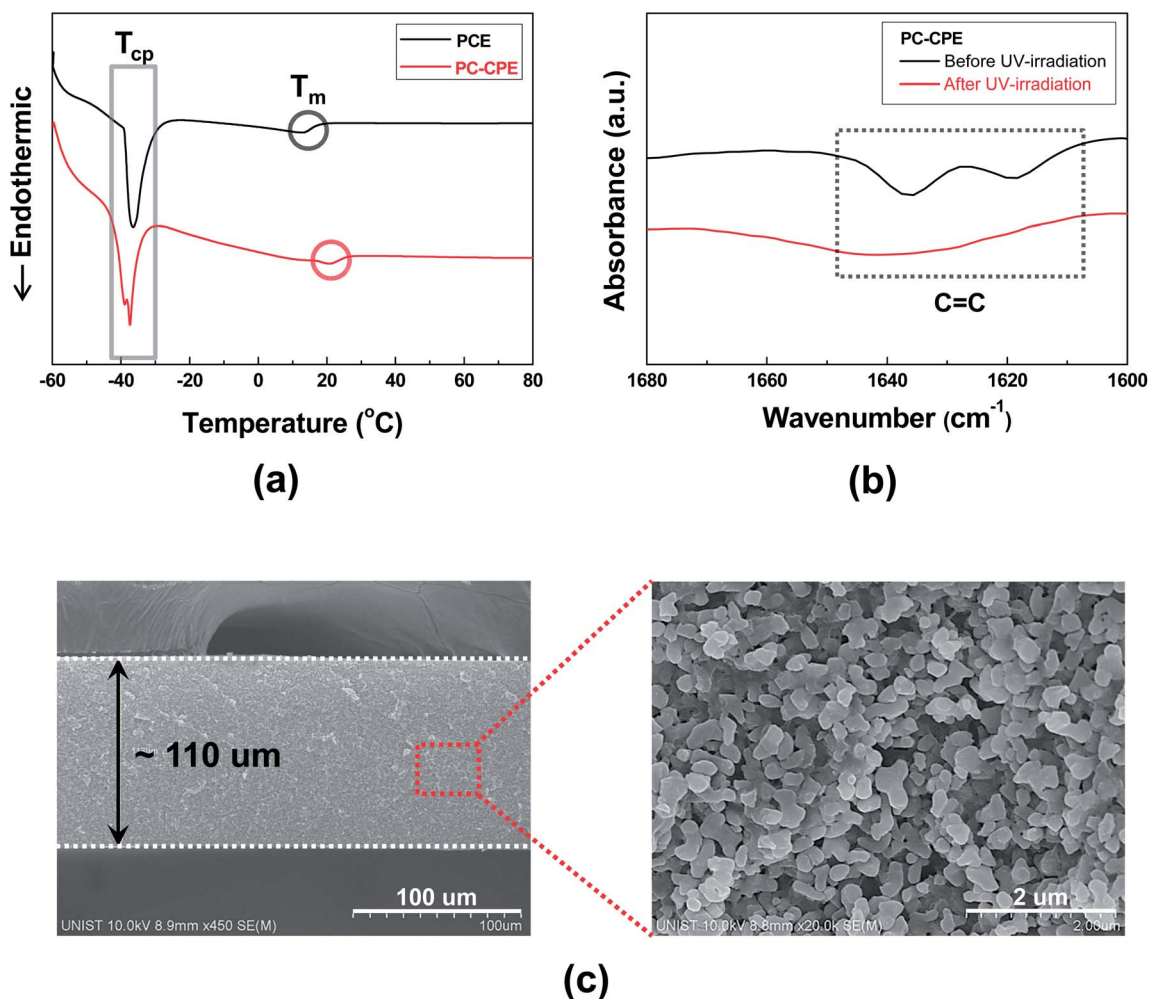


Fig. 1 Structural characterization of PC-CPE: (a) DSC profiles showing characteristic transition temperatures (T_{CP} and T_m) of SN in PCE and PC-CPE; (b) FT-IR spectra (before/after UV curing) of acrylic C=C bonds of ETPTA in PC-CPE; (c) cross-sectional FE-SEM images of PC-CPE, wherein the high-magnification view exhibits the presence of well-reticulated interstitial voids (originally occupied with PCE) formed between the Al_2O_3 nanoparticles.



PCE-soaked $\text{Li}_4\text{Ti}_5\text{O}_{12}$ anode ($\text{Li}_4\text{Ti}_5\text{O}_{12}$ (average particle size (D50) = 10 μm)/PVdF binder/Super-P = 88/10/2 w/w/w). A control cell was fabricated by assembling the same LiCoO_2 cathode and $\text{Li}_4\text{Ti}_5\text{O}_{12}$ anode with a polyethylene (PE) separator (thickness = 20 μm , Tonen), followed by being filled with the carbonate-based liquid electrolyte (1 M LiPF_6 in EC/DMC = 1/1 v/v). The cells were cycled at a constant charge/discharge current density of 0.2 C ($=0.40 \text{ mA cm}^{-2}$)/0.2 C under a voltage range of 1.5–2.7 V. The AC impedance of the cells was measured using the impedance analyzer over a frequency range from 10^{-3} to 10^6 Hz. To explore high-temperature stability of cells incorporating PC-CPE, aluminum (Al) pouch-type cells (width $\times$ length $\times$ thickness = 55 $\times$ 70 $\times$ 0.8 mm/mm/mm) were fabricated and subjected to a thermal shock test. After exposure to the thermal shock condition ($=130^\circ\text{C}/0.5 \text{ h}$), the charge/discharge behavior of cells was monitored at room temperature.

Results and discussion

Structural/electrochemical uniqueness of plastic crystal composite polymer electrolytes (PC-CPEs)

The structural/electrochemical properties of PC-CPEs were characterized, with a focus on its plastic crystal behavior, chemical structure of the UV-cured ETPTA macromer and dispersion state of Al_2O_3 nanoparticles.

The DSC thermograms (Fig. 1a) show that two endothermic peaks assigned to characteristic transition temperatures of SN (T_{CP} (from crystalline to plastic phase) $\sim -39^\circ\text{C}$ and T_{m} (from plastic crystalline phase to melted state) $\sim 13^\circ\text{C}$)^{20–22} are observed in the PC-CPE. Comparison with the thermogram of PCE itself reveals no appreciable difference in the phase transition behavior, which indicates that the introduction of the UV-cured ETPTA/ Al_2O_3 framework does not disrupt the thermal characteristics of PCE. More details about plastic crystal behavior of PCE upon addition of lithium salts and variation of the polymer matrix were described in previous publications.^{20–24}

Another key component of the PC-CPE is the UV-cured ETPTA macromer. Fig. 1b exhibits that the characteristic FT-IR peaks assigned to acrylic C=C bonds^{18,19} of the ETPTA monomer disappeared after exposure to UV irradiation. This result demonstrates that the ETPTA monomer is photo-polymerized under the presence of PCE and Al_2O_3 nanoparticles. In addition to this FT-IR result, the gel content (*i.e.*, insoluble polymer fraction after solvent (DMC followed by acetone) extraction) of the PC-CPE was measured. Above 99% of gel by weight (here, Al_2O_3 nanoparticles are excluded)^{23,24} was observed, which is another evidence to confirm the successful UV curing reaction of the ETPTA monomer.

A cross-sectional FE-SEM image of the PC-CPE (Fig. 1c) shows that the Al_2O_3 nanoparticles are densely packed without serious agglomeration in the through-thickness direction. It is

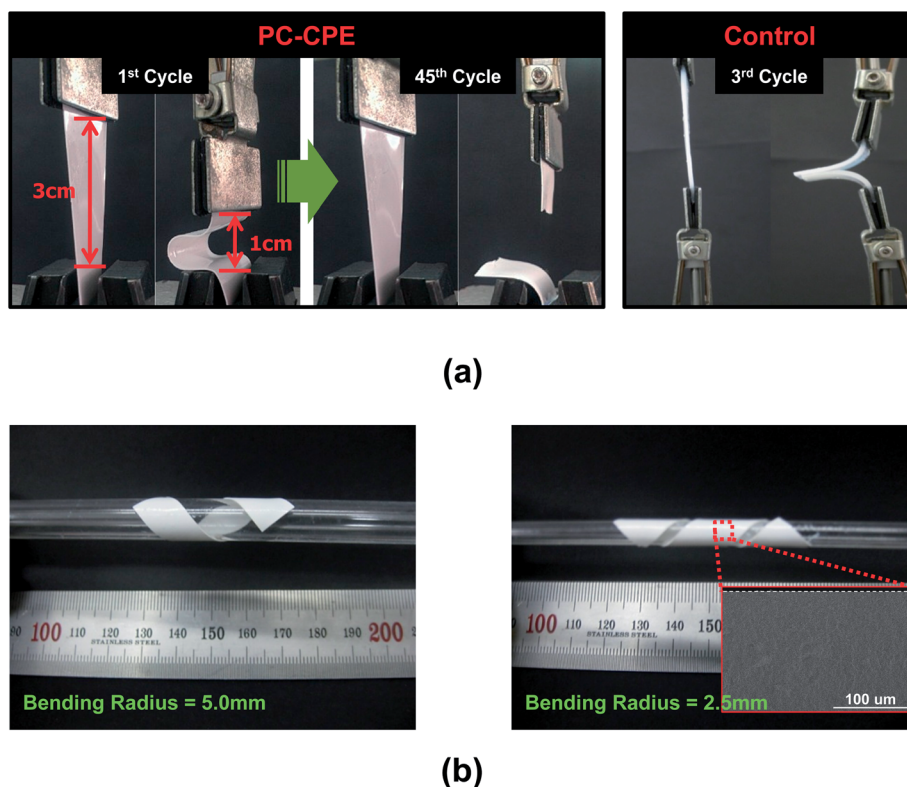


Fig. 2 Mechanical flexibility of PC-CPE: (a) comparison of bendability between PC-CPE and control solid-state electrolyte incorporating no Al_2O_3 nanoparticle, wherein the samples are subjected to repeated bending cycle at a strain rate of 10 mm min^{-1} under longitudinal strain ranging from 1 to 3 cm; (b) photographs of PC-CPE after being wound along a glass rod (diameter = 2.5 and 5 mm), wherein the inset shows that neither micro-scale cracks nor physical defects are formed.



noteworthy that the highly reticulated nanoscale interstitial voids formed between the Al_2O_3 nanoparticles, corresponding to the space originally occupied with PCE that was removed using DMC (as an etching solvent) prior to the SEM measurement, represent the formation of well-networked ion-conductive pathways in the PC-CPE. The larger content of Al_2O_3 nanoparticles ($\text{Al}_2\text{O}_3/(\text{PCE} + \text{ETPTA}) = 66/34$ w/w) and their good compatibility with other components are expected to enable the development of such a unique porous morphology (*i.e.*, highly-interconnected PCE phase in combination with the UV-cured ETPTA/ Al_2O_3 framework). The PCE-based, well-developed ion conductive channels in the PC-CPE are expected to play a crucial role in providing satisfactory level of cell performance, which will be further discussed in the following section.

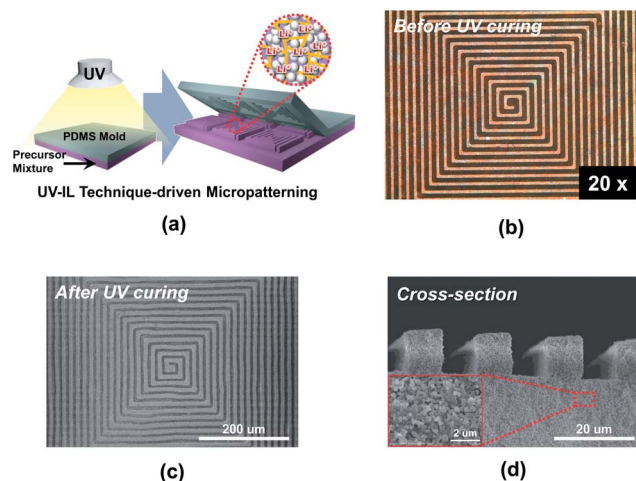


Fig. 3 Structural characterization of maze-patterned PC-CPE: (a) schematic illustration of the UV-IL technique-driven micropatterning procedure; (b) OM image of the PC-CPE precursor mixture prior to UV exposure; (c) FE-SEM image (top view) of microscale maze-patterned PC-CPE; (d) FE-SEM image (cross-sectional view) of microscale maze-patterned PC-CPE, wherein the inset shows that Al_2O_3 nanoparticles are closely packed in the micropatterned PC-CPE.

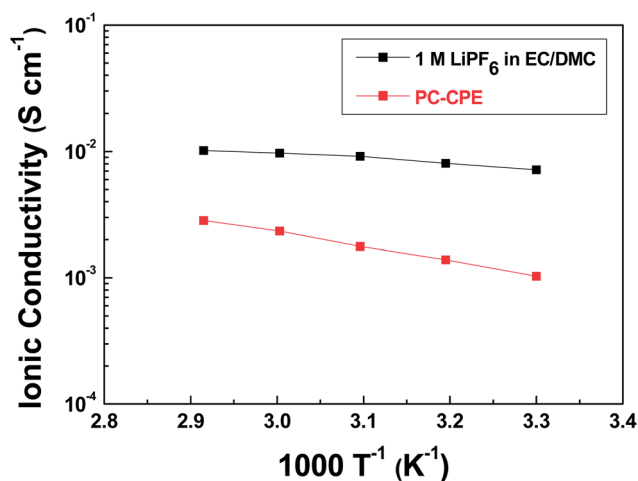


Fig. 4 Temperature-dependent ionic conductivity (temperature range = 30–70 °C) of PC-CPE and carbonate-based liquid electrolyte (1 M LiPF_6 in EC/DMC = 1/1 v/v).

The mechanical flexibility of the PC-CPE was quantitatively examined using a bending test (Fig. 2a). The PC-CPE shows strong resistance to mechanical rupture upon repeated bending cycle (under longitudinal strain ranging from 1 to 3 cm). Comparison with the result of a control sample incorporating no Al_2O_3 nanoparticles verifies that the UV-cured ETPTA/ Al_2O_3 framework effectively contributes to the mechanical bendability of the PC-CPE. While the control sample is broken down just after the 3rd bending cycle, the dimensional stability of the PC-CPE is preserved until the 45th bending cycle. This superior flexibility of the PC-CPE is ascribed to the presence of close-packed Al_2O_3 nanoparticles, which could serve as a mechanical buffer to mitigate stress localization occurring during the repeated bending cycle. It has already been reported that the advantageous effect of well-dispersed nanoparticles on the mechanical toughness of nanocomposites is mainly due to the creation of micro-voids that dissipate external stress.^{26,27} To further underline the excellent mechanical flexibility, the PC-CPE was wound around a glass rod. Fig. 2b shows that no mechanical fracture is observed at the PC-CPE even after being

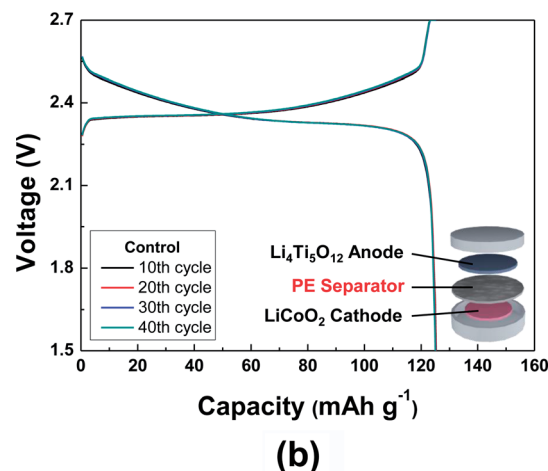
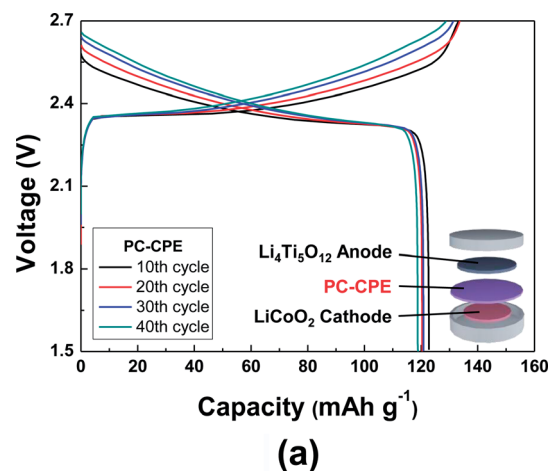


Fig. 5 Charge/discharge profiles of coin-type full cells as a function of cycle number, wherein the cells are cycled at a constant charge/discharge current density of 0.2 C ($=0.40 \text{ mA cm}^{-2}$)/0.2 C under a voltage range of 1.5–2.7 V: (a) $\text{LiCoO}_2/\text{PC-CPE}/\text{Li}_4\text{Ti}_5\text{O}_{12}$; (b) $\text{LiCoO}_2/\text{PE separator}/\text{Li}_4\text{Ti}_5\text{O}_{12}$.

wound around a narrow-diameter rod (≈ 2.5 and 5.0 mm). Moreover, neither micro-scale cracks nor physical defects were found in the PC-CPE (inset of Fig. 2b).

Another noteworthy achievement of the PC-CPE is the provision of a wide range of form factors. The PC-CPE precursor mixture (*i.e.*, prior to UV irradiation) exhibits unique rheological characteristics, in comparison to a conventional carbonate-based liquid electrolyte (here, 1 M LiPF_6 in EC/DMC = $1/1$ v/v) showing low viscosity and Newtonian fluid behavior (Fig. S1, ESI†). Specifically, the viscosity of the PC-CPE precursor mixture is substantially high and also decreases with increasing shear rate, representing a kind of shear-thinning behavior. Details on the rheological behavior of the electrolyte precursor mixture and its influence on the imprinting process were reported in the previous study.¹⁸ A schematic illustration (Fig. 3a) depicts the UV-IL technique-driven micropatterning procedure exploited herein, where pressing maze-patterned PDMS stamp onto the cast slurry of the PC-CPE precursor mixture and subsequent UV irradiation through the transparent PDMS stamp yield self-standing PC-CPE with replica of the maze-pattern. Fig. 3b shows an OM image of the PC-CPE precursor mixture before UV exposure, verifying the formation of the imprinted morphology

with an inversely replicated maze pattern. Morphological characterization based on FE-SEM images (Fig. 3c and d) exhibits that the maze-patterned PC-CPE with finely-defined vertical edges is successfully formed, underlying the fabrication of the solid-state electrolyte with tunable dimensions down to micrometer scale. A high-magnification view (inset of Fig. 3d) demonstrates that Al_2O_3 nanoparticles are closely packed in the micropatterned PC-CPE.

Electrochemical performance of cells assembled with plastic crystal composite polymer electrolytes

The electrochemical performance of cells incorporating PC-CPE was characterized. It should be noted that the cell assembled with the PC-CPE does not incorporate a polyolefin separator membrane, implying that the PC-CPE acts as an electrolyte and also a separator membrane that keeps electrical isolation between electrodes.

The temperature-dependent ionic conductivity of the PC-CPE was measured and compared with that of the carbonate-based liquid electrolyte (1 M LiPF_6 in EC/DMC = $1/1$ v/v) (Fig. 4). Although the ionic conductivity of the PC-CPE was found to be slightly lower than that of the carbonate-based


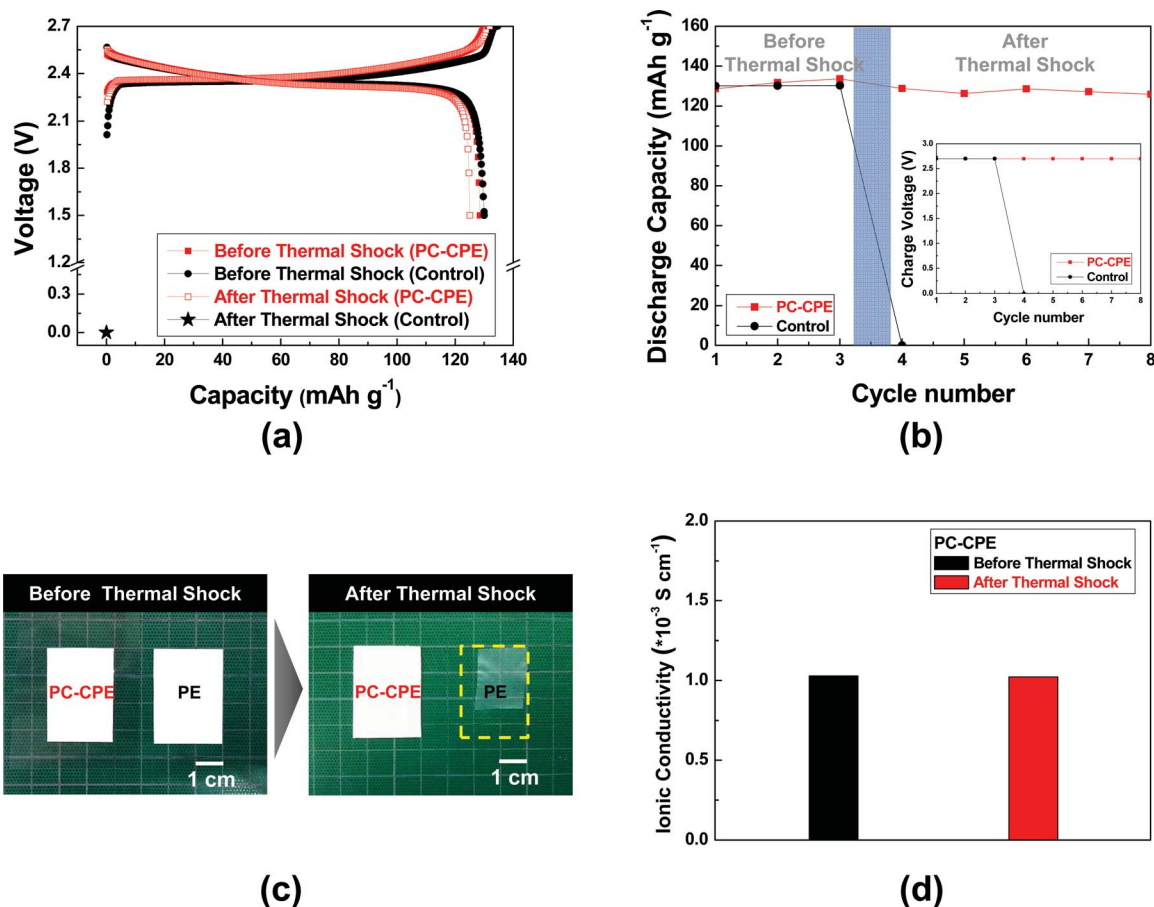


Fig. 6 Thermal stability of Al pouch-type full cells assembled with PC-CPE or carbonate-based liquid electrolyte (1 M LiPF_6 in EC/DMC = $1/1$ v/v) and PE separator: (a) variation in charge/discharge profiles of cells after exposure to thermal shock ($\approx 130^\circ\text{C}/0.5\text{ h}$); (b) variation in discharge capacity and charge voltage (inset) of cells before/after the thermal shock. (c) Comparison of thermal shrinkage between PC-CPE and PE separator after exposure to the thermal shock. (d) Ionic conductivity of PC-CPE before/after the thermal shock.



As another piece of evidence to prove the superior thermal stability of the PC-CPE, the change in cell dimension after the thermal shock test was examined. Fig. 7a shows that the cell incorporating the PC-CPE remains intact without dimensional distortion, in comparison to the control cell that was greatly swollen up. The dynamic mode TGA measurement (Fig. 7b) of the PC-CPE and carbonate-based electrolyte delivers meaningful data to explain this intriguing behavior of cell swelling. Negligible loss in weight was observed at the PC-CPE up to approximately 130 °C, verifying the excellent thermal stability of the PC-CPE. On the other hand, the carbonate-based electrolyte

To attain in-depth understanding of the influence of separators on internal short-circuit failure of cells, dimensional change of the PC-CPE and the PE separator was examined after exposure to the same thermal shock condition (Fig. 6c). The area-based dimensional shrinkage (ΔA) of the PC-CPE was found to be negligibly small, as compared to the PE separator ($\Delta A \sim 43\%$). This result demonstrates that the PC-CPE could act as a self-standing solid-state electrolyte outperforming the PE separator membrane in terms of thermal shrinkage. Commercial PE separators are known to suffer from large thermal

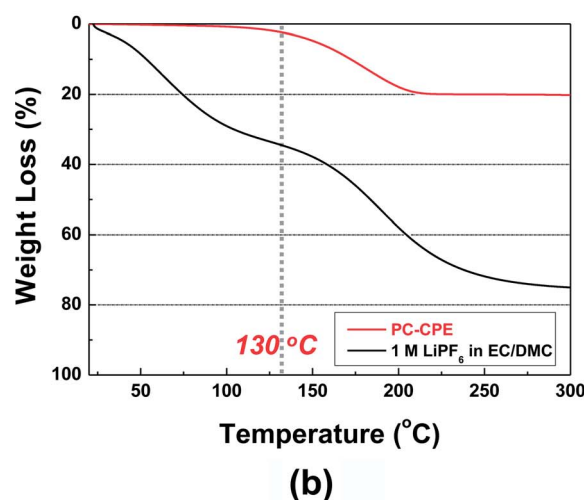

This journal is © The Royal Society of Chemistry 2014

shows the rapid weight loss mainly due to the presence of volatile DMC component (boiling temperature $\sim 90^\circ\text{C}$).^{15,16}

Conclusion

We have presented the PC-CPE as a new class of shape-deformable and thermally stable solid-state electrolyte for flexible/safer lithium-ion batteries. The in-depth structural characterization exhibited that the PCE was successfully combined with the UV-cured ETPTA macromer/close-packed Al_2O_3 nanoparticle framework, leading to the PC-CPE. In comparison to the conventional carbonate-based liquid electrolyte, the PC-CPE provided the remarkable improvement in mechanical properties and thermal stability. The PC-CPE precursor mixture with well-tailored rheological characteristics, in collaboration with the UV-IL process, allowed the development of the PC-CPE featuring microscale maze-pattern. Even after exposure to the thermal shock ($=130^\circ\text{C}/0.5\text{ h}$), the cell incorporating the PC-CPE delivered the stable charge/discharge behavior without suffering from safety problems such as cell swelling and internal short-circuit failure. We believe that the material/structure concept used for fabrication of PC-CPE is simple and versatile, which thus can be readily applicable to a wide variety of next-generation flexible energy storage systems as a platform strategy enabling advanced solid-state electrolytes.

Acknowledgements

This work was supported by the Energy Efficiency and Resources R&D program (20112010100150) under the Ministry of Knowledge Economy, Republic of Korea, Research Fund of the UNIST (Ulsan National Institute of Science and Technology) in 2012, a grant from the R&D Program (Industrial Strategic Technology Development) funded by the Ministry of Knowledge Economy (MKE), Republic of Korea, and the BK21 Plus funded by the Ministry of Education, Korea (10Z20130011057).

References

- 1 M. Armand and J. M. Tarascon, *Nature*, 2008, **451**, 652–657.
- 2 K. Jost, C. R. Perez, J. K. McDonough, V. Presser, M. Heon, G. Dion and Y. Gogotsi, *Energy Environ. Sci.*, 2011, **4**, 5060–5067.
- 3 S. Y. Lee, K. H. Choi, W. S. Choi, Y. H. Kwon, H. R. Jung, H. C. Shin and J. Y. Kim, *Energy Environ. Sci.*, 2013, **6**, 2414–2423.
- 4 G. Zhou, F. Li and H. M. Cheng, *Energy Environ. Sci.*, 2014, **7**, 1307–1338.
- 5 Y. H. Lee, J. S. Kim, J. Noh, I. Lee, H. J. Kim, S. Choi, J. Seo, S. Jeon, T. S. Kim, J. Y. Lee and J. W. Choi, *Nano Lett.*, 2013, **13**, 5753–5761.
- 6 M. R. Palacin, *Chem. Soc. Rev.*, 2009, **38**, 2565–2575.
- 7 G. Jeong, Y. U. Kim, H. Kim, Y. J. Kim and H. J. Sohn, *Energy Environ. Sci.*, 2011, **4**, 1986–2002.
- 8 K. T. Nam, D. W. Kim, P. J. Yoo, C. Y. Chiang, N. Meethong, P. T. Hammond, Y. M. Chiang and A. M. Belcher, *Science*, 2006, **312**, 885–888.
- 9 N. Li, G. Zhou, F. Li, L. Wen and H. M. Cheng, *Adv. Funct. Mater.*, 2013, **23**, 5429–5435.
- 10 X. Jia, Z. Chen, X. Cui, Y. Peng, X. Wang, G. Wang, F. Wei and Y. Lu, *ACS Nano*, 2012, **6**, 9911–9919.
- 11 A. Vlad, A. L. M. Reddy, A. Ajayan, N. Singh, J. Gohy, S. Melinte and P. M. Ajayan, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 15168–15173.
- 12 N. Li, Z. Chen, W. Ren, F. Li and H. M. Cheng, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 17360–17365.
- 13 H. Gwon, H. S. Kim, K. U. Lee, D. H. Seo, Y. C. Park, Y. S. Lee, B. T. Ahn and K. Kang, *Energy Environ. Sci.*, 2011, **4**, 1277–1283.
- 14 L. Hu and Y. Cui, *Energy Environ. Sci.*, 2012, **5**, 6423–6435.
- 15 K. Xu, *Chem. Rev.*, 2004, **104**, 4303–4417.
- 16 E. Quartarone and P. Mustarelli, *Chem. Soc. Rev.*, 2011, **40**, 2525–2540.
- 17 J. Hassoun, S. Panero, P. Reale and B. Scrosati, *Adv. Mater.*, 2009, **21**, 4807–4810.
- 18 E. H. Kil, K. H. Choi, H. J. Ha, S. Xu, J. A. Rogers, M. R. Kim, Y. G. Lee, K. M. Kim, K. Y. Cho and S. Y. Lee, *Adv. Mater.*, 2013, **25**, 1395–1400.
- 19 S. H. Kim, K. H. Choi, S. J. Cho, E. H. Kil and S. Y. Lee, *J. Mater. Chem. A*, 2013, **1**, 4949–4955.
- 20 P. J. Alarco, Y. Abu-Lebdeh, A. Abouimrane and M. Armand, *Nat. Mater.*, 2004, **3**, 476–481.
- 21 S. Das, S. J. Prathapa, P. V. Menezes, T. N. Row and A. J. Bhattacharyya, *J. Phys. Chem. B*, 2009, **113**, 5025–5031.
- 22 L. Z. Fan, Y. S. Hu, A. J. Bhattacharyya and J. Maier, *Adv. Funct. Mater.*, 2007, **17**, 2800–2807.
- 23 H. J. Ha, E. H. Kil, Y. H. Kwon, J. Y. Kim, C. K. Lee and S. Y. Lee, *Energy Environ. Sci.*, 2012, **5**, 6491–6499.
- 24 K. H. Choi, S. J. Cho, S. H. Kim, Y. H. Kwon, J. Y. Kim and S. Y. Lee, *Adv. Funct. Mater.*, 2014, **24**, 44–52.
- 25 J. Yao, A. P. Le, M. V. Schulmerich, J. Maria, T. W. Lee, S. K. Gray, R. Bhargava, J. A. Rogers and R. G. Nuzzo, *ACS Nano*, 2011, **5**, 5763–5774.
- 26 H. E. H. Meijer and L. E. Govaert, *Prog. Polym. Sci.*, 2005, **30**, 915–938.
- 27 B. Cotterell, J. Y. H. Chia and K. Hbaieb, *Eng. Fract. Mech.*, 2007, **74**, 1054–1078.
- 28 P. Arora and Z. Zhang, *Chem. Rev.*, 2004, **104**, 4419–4462.
- 29 E. S. Choi and S. Y. Lee, *J. Mater. Chem.*, 2011, **21**, 14747–14754.

