

Cite this: *Mater. Adv.*, 2021,
2, 2075

Mn²⁺ activated Ca- α -SiAlON – broadband deep-red luminescence and sensitization by Eu²⁺, Yb²⁺ and Ce³⁺†

Atul D. Sontakke,^{ib}*^a Arnoldus J. van Bunningen,^a Sadakazu Wakui^{ab} and Andries Meijerink^{*a}

The covalent character of (oxy)nitrides has enabled tuning of emission color for new Eu²⁺- and Ce³⁺-doped phosphors and widespread implementation in white light LEDs. Mn²⁺-doped (oxy)nitrides form a relatively unexplored class of luminescent materials with great potential as orange to near infrared (NIR) phosphor in white light and NIR LEDs. Here we report deep red broad band emission around 700 nm for Mn²⁺ in Ca- α -SiAlON. The emission shows a complex and gradual temperature quenching behavior and an unexpectedly large blue shift of the band maximum from 740 nm at 75 K to 670 nm at 475 K. This peculiar luminescence behavior is explained by disorder in the local (N,O)₇ polyhedral coordination of the Mn²⁺ ions resulting in a variation in emission maximum and quenching temperature for differently coordinated Mn²⁺ ions. Interestingly, the present results deviate from previous reports on narrow band orange emission from Mn²⁺ in Ca- α -SiAlON. Careful analysis reveals that the orange emission likely originates from an AlN:Mn²⁺ impurity phase. Sensitization of the Mn²⁺ emission by strongly absorbing Eu²⁺, Yb²⁺ and Ce³⁺ ions was observed but with low efficiency as energy transfer to Mn²⁺ via exchange interaction is ineffective for the relatively large (>5 Å) nearest neighbor separation in Ca- α -SiAlON. The new insights on Mn²⁺ emission show that for efficient orange/red emission in (oxy)nitrides, a tetrahedral coordination is required for Mn²⁺ while deep red/NIR emission can be expected for higher coordination numbers but is prone to thermal quenching. Sensitization of the Mn²⁺ emission is efficient only for exchange interaction and requires short (<5 Å) nearest neighbor separation.

Received 15th January 2021,
Accepted 21st February 2021

DOI: 10.1039/d1ma00036e

rsc.li/materials-advances

A Introduction

Nitride and oxynitride compounds have emerged as efficient hosts for phosphor applications, and are widely commercialized.¹ Although their synthesis is non-trivial and requires special processing conditions, they have the ability to achieve superior structural rigidity and their higher bond covalency offers unique optical properties that are difficult to achieve in oxides and other traditional hosts. This has primarily been exploited to achieve efficient red emitting phosphors, such as (Ca,Sr)AlSiN₃:Eu²⁺ (CASN:Eu²⁺ or CSASN:Eu²⁺),^{2,3} (Sr,Ba)₂Si₅N₈:Eu²⁺,^{4,5} SrLiAl₃N₄:Eu²⁺ (SLA:Eu²⁺),⁶ Sr[Li₂Al₂O₂N₂]:Eu²⁺ (SALON:Eu²⁺),⁷ *etc.* The dopant ions surrounded by a nitrogen-rich covalent anionic coordination exerts a large nephelauxetic shift, which together with strong

crystal field and rigid lattice network allow longer wavelength and relatively narrow-band emission with superior thermal stability.

In view of the recent search for narrow-band emitting phosphors for wider color gamut displays and higher efficacy (lumen/watt) lighting, nitride and oxynitride based phosphors attracted special attention. Hoerder *et al.*, have demonstrated record narrow-bandwidth for Eu²⁺ red emission in SALON with full width at half maximum (FWHM) of about 48 nm.⁷ In addition to Eu²⁺, also Mn²⁺ ions are promising activator ions to achieve narrow band emission. AlN:Mn²⁺ reveals crisp orange photoluminescence (PL) with a FWHM of about 43 nm.^{8–10} Mn²⁺ even offers great spectral tunability depending on crystal field strength (d⁵-configuration), coordination symmetry and bond covalency. In tetrahedral coordination, such as in AlON, Mn²⁺ exhibits green ⁴T₁ → ⁶A₁ emission (λ_{peak} : 515 nm, FWHM: 32–44 nm),¹¹ whereas orange-red emission is achieved in AlN (λ_{peak} : 600 nm, FWHM: 43 nm)¹⁰ and ZnGeN₂ (λ_{peak} : 610 nm, FWHM: 49–54 nm) because of reduced splitting between free ion states by a stronger nephelauxetic effect.^{12,13} In octahedral or similar stronger crystal field coordination the ⁴T₁ → ⁶A₁ energy

^a Condensed Matter & Interfaces, Debye Institute for Nanomaterials Science, Utrecht University, Princetonplein 1, 3584 CC Utrecht, The Netherlands.

E-mail: a.d.sontakke@uu.nl, a.meijerink@uu.nl

^b Nichia Corporation, 491 Oka, Kaminaka-Cho, Anan-Shi, Tokushima 774-8601, Japan

† Electronic supplementary information (ESI) available: PL and PLE spectra, XRD patterns and PL decay curves, *etc.* See DOI: 10.1039/d1ma00036e



gap decreases and this shifts Mn^{2+} emission further into the red to near-infrared (NIR) region and also its spectral shape relatively broadens (FWHM > 60 nm).^{14–16} In CASN: Mn^{2+} , two emissions bands (λ_{peak} : 548 nm, 627 nm) were reported and attributed to Mn^{2+} ions occupying pentahedral Ca site and tetrahedral Al site respectively, with a combined FWHM of 100 nm.¹⁵ For a similar compound, $\text{MgAlSi}_3\text{N}_5\text{:Mn}^{2+}$ an even broader emission in deep-red to NIR region (λ_{peak} : 754 nm, FWHM: 150 nm) was observed arising from Mn^{2+} ions at the pentahedral Mg site [MgN_5].¹⁶

Recently in few studies, Mn^{2+} doped Ca- α -SiAlON was reported to exhibit orange emission with a relatively narrow bandwidth (λ_{peak} : 600 nm, FWHM about 45 nm).^{17–19} However, when codoped with sensitizer ions, such as Eu^{2+} , no sensitized Mn^{2+} orange emission was observed.²⁰ Ca- α -SiAlON:Eu²⁺ exhibits bright yellow d-f emission. On Mn^{2+} codoping, the Eu²⁺ emission exhibited a steady decrease revealing energy transfer related quenching, but the absence of sensitized Mn^{2+} emission was striking.^{19,20} Moreover, it is anticipated that the Mn^{2+} ions occupy the seven coordinated Ca²⁺ polyhedral sites in Ca- α -SiAlON, which would lead a rather broader Mn^{2+} emission spectral shape.²⁰ The reported narrow band emission would require Mn^{2+} ions to occupy tetrahedral sites, such as Al or Si, which are fairly small in Ca- α -SiAlON and thus are less likely to incorporate Mn^{2+} dopants.

Ca- α -SiAlON is a solid-solution of Ca, Si, Al, O and N and is iso-structural to α - Si_3N_4 (Fig. 1).²¹ Amongst several polymorphs of Si_3N_4 , α and β structural phases based SiAlON compositions, when activated using appropriate dopants exhibit excellent phosphor properties.^{22–24} The structures in both phases consist of a three-dimensional network of interconnected tetrahedral [SiN_4] units, but primarily differ in their stacking orientation along *c*-axis. The α phase exhibits ABCD-type stacking over ABAB-type stacking in β phase. This leads to a continuous set of channels along *c*-direction in β phase, but in α phase, these channels are blocked and instead form voids. Unlike the pure substitutional composition in the β phase ($\text{Si}_{6-z}\text{Al}_z\text{O}_z\text{N}_{8-2z}$, where $z = 0-4.2$), the α phase offers two interstitial sites (voids) of crystallographically identical nature per unit cell. These sites

can be occupied by a charge-stabilizing cation, Me (Fig. 1) and give rise to chemical compositions $\text{Me}_x\text{Si}_{12-(m+n)}\text{Al}_{m+n}\text{O}_n\text{N}_{16-n}$. In α -SiAlON, $m + n$ (Si-N) bonds are replaced by m (Al-N) and n (Al-O) bonds, and the charge difference is compensated by incorporation of Me cations. Here, Me can be Li, Mg, Ca, Sr, Y or Ln ions and $x = m/\nu$, where ν is charge on Me cation.²⁵ The Me cations occupy interstitial sites available in lattice structure and are coordinated with seven anions (N,O) with three different Me-(N,O) distances.

The Me- α -SiAlON compounds show high solubility for several dopant ions, such as Eu^{2+} , Ce^{3+} , Pr^{3+} , Sm^{2+} , Tb^{3+} , Dy^{3+} , Yb^{2+} , etc.^{26–29} Previous studies suggested Me = Ca and $m \sim 2$ exhibits superior phosphor properties.^{26,28} Among several dopant ions, Eu^{2+} , Ce^{3+} and Yb^{2+} exhibit intense f-d type allowed transitions and have extensively been investigated as LED phosphors.^{26–28} As mentioned earlier,^{17–19} a few studies have reported Mn^{2+} -doped Ca- α -SiAlON, however the spectroscopic observations contradict structural considerations, particularly the narrow-band emission profile, and therefore demand further careful investigation. In present work, we studied Mn^{2+} doping in Ca- α -SiAlON and investigated its photoluminescence properties in detail. Accordingly, Mn^{2+} -doped Ca- α -SiAlON shows broad deep-red luminescence, in line with Mn^{2+} substitution at Ca²⁺ polyhedral site. The previous reports of narrow-band orange Mn^{2+} PL is explained by trace amounts of AlN:Mn impurities. Moreover, we investigate sensitization of the Mn^{2+} emission in Ca- α -SiAlON. Sensitization is observed but the wide dopant site separation (> 5 Å) makes sensitization of Mn^{2+} ions inefficient with sensitizer ions such as Eu^{2+} , Ce^{3+} or Yb^{2+} .

B Materials and methods

Synthesis

All samples investigated in the present work were obtained by the solid-state reaction method. High purity reagent grade chemicals of Si_3N_4 (SN-E10 grade, Ube Chemicals, Japan), AlN (99.9%, Sigma-Aldrich, Germany), CaCO_3 (99.9%, Merck), BaCO_3 (99.9%, Merck), MnCO_3 (99.9%, Sigma-Aldrich, Germany), MnF_2 (99.99%, Sigma-Aldrich, Germany), EuF_3 (99.99%, Highway Chemicals, NL), YbF_3 (99.99%, Highway Chemicals, NL) and CeF_3 (99.99%, Highway Chemicals, NL) were used. The precursor chemicals were weighed in a stoichiometric ratio and mixed thoroughly using agate mortar-pestle. Acetone was used as dispersant during mixing. In doped samples, the respective dopant ions were incorporated by substituting equivalent metal ions (Ca^{2+}) contents in atomic % (at%), i.e. $\text{Ca}_{1-x-y}\text{Si}_9\text{Al}_3\text{O}_n\text{N}_{15+x}\text{Mn}_y(\text{Eu}/\text{Yb}/\text{Ce})$, where $x = 0-15$ at% and $y = 0, 0.5$ at%. The well-mixed powder batches were transferred into covered BN crucibles and fired at high temperature under 10% H_2 -90% N_2 gas-flow reducing atmosphere. The sintering temperature for Ca- α -SiAlON was set at 1650 °C for 5 hours dwell time, unless specified otherwise in the text. The ramp rate was 200 K hour⁻¹. To compare, Mn^{2+} doped $\text{BaSi}_3\text{Al}_3\text{O}_4\text{N}_5$ (5 at% Mn) and AlN (1 at% Mn) samples

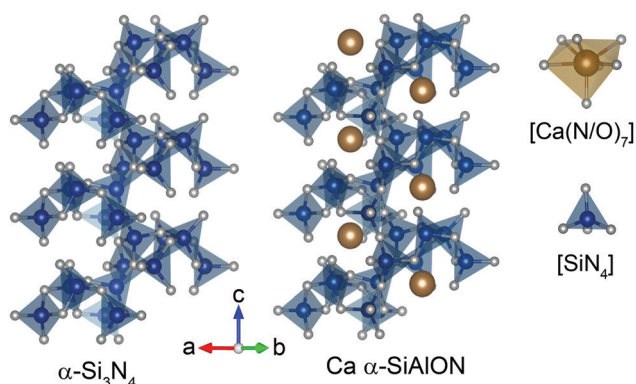


Fig. 1 Crystal structure of α - Si_3N_4 and Ca- α -SiAlON along *c*-axis. The brown, blue and gray spheres represent Ca, Si/Al, and N/O ions, respectively. The coordination polyhedron of Ca and Si tetrahedron are presented in right side.



were also obtained using same synthesis conditions (1650 °C for 5 hours dwell time). The sintered powders were then mildly crushed to fine powders using agate mortar-pestle and used for experimental analysis. The Ca- α -SiAlON samples are identified using dopant contents throughout the manuscript and other samples are detailed according to their composition, sintering temperature and doping contents, wherever necessary in the text.

Experimental methods

The obtained samples were analyzed using powder X-ray diffraction (PXRD) method for phase identification and purity. A Bruker D2 PHASER X-ray diffractometer with Co target ($\lambda_{K\alpha} = 1.78897 \text{ \AA}$) was used at 30 kV operating voltage and 10 mA current. The step size resolution was 0.01 \AA . Another X-ray diffractometer with Cu target ($\lambda_{K\alpha} = 1.5401 \text{ \AA}$) from Philips was also used at 40 kV operating voltage and 20 mA current. Photoluminescence (PL) spectroscopy was performed using an Edinburgh Instruments FLS-920 fluorescence spectrometer. The PL and PL excitation (PLE) measurements were recorded using a 450 W Xe lamp as excitation source and a Hamamatsu R928 photomultiplier tube (PMT) detector and a liquid nitrogen cooled NIR detector. The spectral resolution was maintained at 0.5 nm in UV-visible range and 1 nm in near-infrared range for both PL and PLE measurements. For PL decay measurement, a picosecond pulsed laser diode (Edinburgh Instruments EPL 375, peak wavelength: 376.5 nm, pulse width: 65 picoseconds) was used as excitation source and the signals were recorded using Hamamatsu H74220-60 fast response PMT. The decay curves were recorded using single photon counting method with 4000 channels resolution. For normal full range (10 μs) decay curve, each channel provides 2.4 ns resolution. For higher resolution (HR) decay measurements, the channel width was reduced to 0.048 ns. Mn^{2+} PL decay measurement was performed by using a tunable optical paramagnetic oscillator (OPO) Opotek Opolette HE 355II pulsed laser (pulse width: 10 ns; repetition rate: 10 Hz) as excitation source, and the emission was recorded by a liquid nitrogen cooled NIR detector. For cryogenic (4.2 K) measurements, the samples were cooled down using an Oxford Instruments liquid He flow cryostat. For temperature dependence study, liquid He flow cryostat was employed in the 4.2–500 K temperature range, whereas a temperature-controlled stage from Linkam Scientific (THMS600) was used for the 300–600 K temperature range. For data analysis and plotting, Origin Lab (9.1 version) software was used. All curve fittings were performed using orthogonal distance regression algorithms. The crystal structure and radial ionic distribution analysis was carried out using the VESTA (3.4.4 version) software.

C Results and discussion

The powder X-ray diffraction (PXRD) patterns of undoped and Mn^{2+} (10 at%) doped Ca- α -SiAlON powders are presented in Fig. 2a. The diffraction patterns of all samples reveal

single-phase trigonal α - Si_3N_4 type crystal structure with $P31c$ space group.²¹ No detectable impurity phases could be observed. In the undoped sample, the pattern reflects the Ca- α -SiAlON structure corresponding to $\text{CaSi}_9\text{Al}_3\text{ON}_{15}$ composition with cell parameters of $a = 7.850 \text{ \AA}$ and $c = 5.717 \text{ \AA}$.¹⁹ On Mn^{2+} doping, the peak position and shape profile shows significant differences when doped using MnCO_3 (oxide) precursor, whereas, the MnF_2 (fluoride) precursor doping did not reveal noticeable changes compared to the undoped sample. In oxide precursor doped samples, the diffraction peaks are broader and shift towards higher diffraction angle compared to the undoped Ca- α -SiAlON. The peak shift suggests a lattice contraction, which is expected considering the substitution of larger sized Ca^{2+} ions by smaller Mn^{2+} dopant ions.²⁰ The peak broadening typically indicates a reduced particle size, causing a broader distribution of lattice plane distances.

Contrarily, the diffraction pattern of the fluoride precursor doped sample did not reveal a peak shift compared to the undoped Ca- α -SiAlON and the peak broadening is also insignificant. This suggests that the fluoride content affects structural properties. Normally in high temperature solid-state reaction synthesis, fluoride-based contents act as flux to aid and accelerate the sintering reaction, and are often intentionally incorporated.^{30–32} The PXRD results indeed suggest a better crystallinity in MnF_2 -doped sample over the MnCO_3 -based sample. It is also believed that the lack of oxygen during firing stage forces fluorine to play an anionic role in the lattice structure. Each oxygen vacancy requires two fluorine anions for charge compensation. The presence of large voids in α -SiAlON structure, where only half of them are occupied with Ca sites in studied composition, indicates that the charge compensating anionic impurities, such as excess fluorine anions, can easily be accommodated at interstitial position. The presence of excess ions (fluorine anions) may thus counter the contraction effect due to Mn^{2+} substitution with Ca^{2+} . This may explain the peculiar observation of diffraction pattern of MnF_2 doped Ca- α -SiAlON. However, a proper reasoning requires more detailed structural studies, and is out of the scope of present investigation.

Fig. 2b presents the PL–PLE properties of undoped and Mn^{2+} -doped Ca- α -SiAlON powders. An intense, broad deep-red PL is observed in Mn^{2+} -doped samples under Mn^{2+} -ligand charge transfer (255 nm) excitation. The PL peak position is situated at around 697 nm with a full width at half-maximum (FWHM) of about 200 nm ($\sim 480 \text{ meV}$). The emission is assigned to the ${}^4\text{T}_1 \rightarrow {}^6\text{A}_1$ transition based on the d^5 Tanabe–Sugano diagram. Note that, based on the deviation of the local coordination from octahedral symmetry, the ${}^4\text{T}_1$ state will be split but it is customary to describe the Mn^{2+} emission with the irreducible representation labels for octahedral symmetry even when the actual site symmetry is lower. The Mn^{2+} PL shape profile is independent of the doping precursor type (MnCO_3 or MnF_2) suggesting that the Mn^{2+} local coordination remains unaffected (ESI,† Fig. S1). It is noticed that the Mn^{2+} PL intensity is slightly higher in fluoride precursor doped sample. This difference becomes more pronounced for excitations in





Fig. 2 PXRD patterns of undoped and Mn²⁺ (10 at%) doped Ca- α -SiAlON obtained using oxide and fluoride doping precursors (a); respective PL–PLE spectra (b); the photographic images (powders filled in quartz disks) under day-light and UV-light (254 nm Hg vapor lamp) exposure (c); and the Mn²⁺ PL decay curves (d). The reference XRD pattern in (a) was calculated for Ca- α -SiAlON structure ($\lambda_{K\alpha} = 1.78897$ Å). In (b), the excitation wavelength was 255 nm for PL measurements and the emission was monitored at 695 nm to record the PLE spectra. The insets present enlarged view (10 times) of PL–PLE curves in 300–600 nm range.

the d–d absorption bands ($\lambda > 325$ nm). This is clearly visible from the enlarged view of PLE spectra (insets, Fig. 2b), where the d–d excitation bands are more pronounced in MnF₂ doped sample than for the MnCO₃ doped sample. The results indicate that the fluoride precursor is more effective in Mn²⁺ incorporation in the Ca- α -SiAlON lattice and also improves the PL properties. In line with the PL, the PLE shape of d–d transitions in both fluoride and oxide doping precursor samples are similar (ESI,† Fig. S2). The PLE spectrum shows weak (spin- and parity forbidden) broad band excitation between 450 and 600 nm corresponding to ${}^6A_1 \rightarrow {}^4T_1, {}^4T_2$ transitions and a weak sharp excitation line due to the ${}^6A_1 \rightarrow {}^4A_1, {}^4E$ transition around 445 nm. Note that the wavelength of the sharp ${}^6A_1 \rightarrow {}^4A_1, {}^4E$ excitation line is at longer wavelength than typically observed (~ 410 – 425 nm) for Mn²⁺ in oxides because of the stronger nephelauxetic effect. A weak UV-blue PL is also observed and attributed to the host Ca- α -SiAlON as it is also present in undoped sample. The intensity of this host emission is weaker in Mn²⁺-doped samples.

The photographic images of undoped and Mn²⁺-doped Ca- α -SiAlON powders under daylight and under UV-light (254 nm) are presented in Fig. 2c. All three samples exhibit a clear white body color. The spin-and-parity forbidden d–d transitions in Mn²⁺ are too weak to cause visible coloration even at 10 at% doping concentration. Under UV-irradiation, the Mn²⁺-doped samples exhibit bright red colored glow, whereas the undoped Ca- α -SiAlON powder exhibits a faint violet-gray appearance (the blue-colored tint at peripheral border is originating from quartz disks used to hold the powders). Fig. 2d presents the Mn²⁺ PL decay curves in oxide and fluoride precursor doped Ca- α -SiAlON. The decay curves in both samples show similar relaxation kinetics, which further supports the earlier claim that the Mn²⁺ local coordination in Ca- α -SiAlON doped with either MnCO₃ or MnF₂ is similar.

The overall results in Fig. 2 suggest that the Mn²⁺ doping in Ca- α -SiAlON is more effective using fluoride (MnF₂) doping precursor, and therefore for further investigations, we only used fluorides as doping precursors. To study the effect of doping concentration on PL properties, Ca- α -SiAlON doped with 1–15 at% Mn²⁺ contents were prepared. Phase purity of prepared samples was confirmed using PXRD measurements (ESI,† Fig. S3). Fig. 3a presents the Mn²⁺ PL in Ca- α -SiAlON as a function of doping concentrations. The PL intensity shows a steep increase from 1 at% to 5 at% doping, but then decreases slowly for further increase in doping concentrations. From PLE

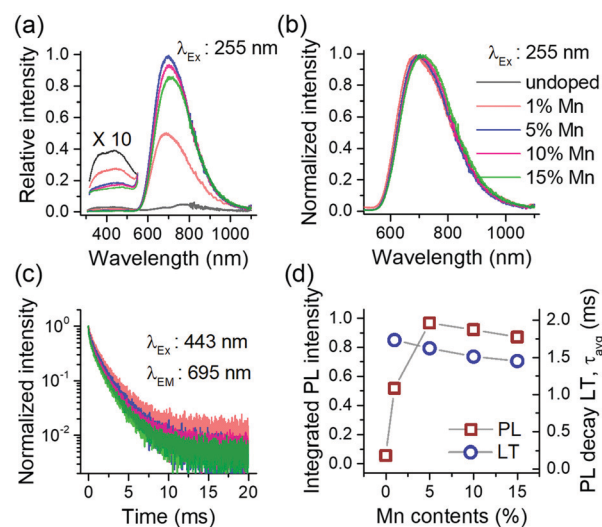


Fig. 3 Concentration dependent PL (a); PL spectra in normalized scale (b); PL decay curves (c); and the plot of integrated PL intensity and luminescence decay times vs. concentration in Mn²⁺ activated Ca- α -SiAlON (d). In (a), (b) and (c), the line colors as indexed in (b) identify respective concentrations.



spectra, the optimum Mn^{2+} concentration is found to be 5 at% under charge transfer excitation (<300 nm), whereas it is 10 at% under d–d transitions excitation (ESI,† Fig. S4). The normalized PL spectra are presented in Fig. 3b. The PL exhibits small redshift with increase in Mn^{2+} concentration. A concentration dependent PL redshift is often obvious and similar observations have also been reported in Eu^{2+} (or Ce^{3+}) doped $\text{Ca-}\alpha\text{-SiAlON}$.^{26,33} It may arise from energy transfer among optically active ions or due to subtle differences in crystal field by progressive substitution of host cations with dopant ions, or both.

The Mn^{2+} PL decay curves for different doping concentration is presented in Fig. 3c. All decay curves reveal non-exponential decay kinetics and exhibit faster relaxation with increase in concentration. The average decay lifetime (LT) was derived from the decay curve fitting using multi-exponential function (ESI,† Fig. S5). The slow decay component in least doped sample (Mn^{2+} concentration 1 at%) indicates that the radiative LT is about 2–2.5 ms for Mn^{2+} PL in $\text{Ca-}\alpha\text{-SiAlON}$. This value is reasonable when compared to oxide (>5 ms to several tens of ms) and nitride (a few ms) hosts.^{8,16,34} Typically, selection rules become more relaxed as covalency increases as it leads to increased mixing of electronic states. This explains the trend towards shorter Mn^{2+} PL life times from fluorides to oxides to nitrides. Fig. 3d presents a plot of integrated PL intensity and LT with doping concentration. The PL intensity first increases till a 5 at% doping level and then decreases for a further increase in doping contents under 255 nm excitation. The LT exhibits a steady decrease with increase in concentration. It is interesting to note that both PL and LT slowly decrease with concentration, indicating that the Mn–Mn interactions are rather weak in $\text{Ca-}\alpha\text{-SiAlON}$ and prevent strong concentration quenching.

Fig. 4a presents the temperature dependence of Mn^{2+} PL in $\text{Ca-}\alpha\text{-SiAlON}$ under charge transfer (275 nm) excitation. It shows that the PL intensity steadily decreases above 25 K, and the shape profile slightly broadens with increase in temperature. A careful analysis of PL peak shift reveals that it exhibits an initial redshift till ~ 50 K and then continuously blueshifts for further increase in temperature. The normalized PL spectra show the PL shift and broadening effect more clearly (Fig. 4b). Accordingly, the PL peak exhibits a whopping 70 nm shift (740 nm to 670 nm) for temperature increase from 75 K to 475 K. Comparatively, the broadening effects appear small, *i.e.* FWHM is about 185 nm (~ 420 meV) at 4.2 K, 197 nm (~ 480 meV) at 300 K, and is about 198 nm (~ 510 meV) at 475 K. The PL broadening with temperature primarily occurs due to increased vibronic (Stokes and anti-Stokes emissions) transitions originating from thermal population of higher vibrational levels.^{35,36} The vibronic effect can clearly be seen from the increased intensity of higher energy side emission in PL spectra (Fig. 4a) despite the overall PL quenching with increase in temperature. The relative contribution of vibronic transitions together with crystal field variations (lattice expansion/contraction) with temperature and other temperature-induced effects, such as lower PL quenching temperatures for Mn^{2+}

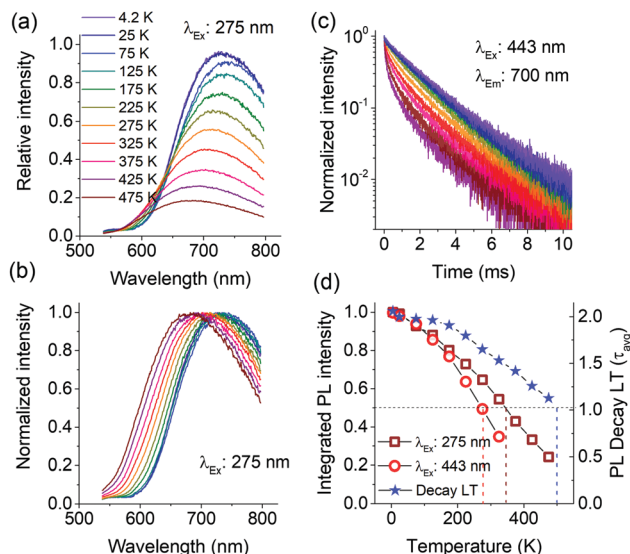


Fig. 4 Temperature dependent PL of Mn^{2+} (10 at%) doped $\text{Ca-}\alpha\text{-SiAlON}$ under 275 nm excitation (a); PL in normalized scale (b); PL decay curves (c); and the plot of integrated PL intensity (under 275 nm and 443 nm excitations) and the PL decay time with temperature (d). In (a), (b) and (c), the line colors are as indexed in (a). In (d), the integrated PL values were derived from 535–800 nm spectral range.

emitting at longer wavelengths, determine the PL peak shift. The lower quenching temperature of deep red/NIR emitting Mn^{2+} centers can explain the unusually large blue shift between 75 and 475 K and will be discussed below.

Interestingly, even at 4.2 K, in the PL spectra no vibronic fine structure is observed, suggesting a larger Huang–Rhys factor for Mn^{2+} PL in $\text{Ca-}\alpha\text{-SiAlON}$ (ESI,† Fig. S6).³⁷ This is also in agreement with the large Stokes shift observed in luminescence spectra for $\text{Ca-}\alpha\text{-SiAlON}$ activated with Eu^{2+} and other ions.²⁶ This has been attributed to the size mismatch of dopant ions with the site occupied in the $\alpha\text{-SiAlON}$ lattice structure, which allows extended configurational changes during excitation–relaxation dynamics in dopants’ electronic structure.³⁸

The large Stokes shift also reflects a low energy threshold for configuration crossover between excited and ground states, thus allowing thermally activated PL quenching at relatively lower temperature.^{39–42} Fig. 4d presents the temperature dependence of integrated PL intensities under charge transfer (275 nm) and d–d excitation (443 nm), as well as the PL decay times. The plot shows that the PL exhibits a monotonous decrease above 25 K. Under charge transfer excitation, the 50% of PL intensity occurs at ~ 350 K, but still the PL does not completely quench even till 475 K. A typical thermal quenching behavior exhibits a sharp decrease in PL (or decay time) above the threshold quenching temperature.^{39–43} In present case, the PL decrease is continuous. This observation suggests that there is a range of dopant sites exhibiting different quenching temperatures. To substantiate this, the temperature dependence of PL intensity under d–d excitation (443 nm) and of the PL decay curves were recorded. The PL under 443 nm excitation shows similar gradual decrease with increase in



temperature, but the decrease is relatively faster with T50% occurring at 280 K (Fig. 4d). Additionally, the peak shift under 443 nm excitation is larger compared to charge transfer excitation (ESI,† Fig. S7). Fig. 4c presents the temperature dependence of PL decay curves under 443 nm excitation. The decay curve at low temperature (4.2 K) does not show perfect single exponential decay kinetics, but instead is composed of multi-exponential decay components. With increase in temperature, the non-exponential nature becomes more prominent and exhibits faster relaxation kinetics, characteristic of temperature induced PL quenching. The emission LT derived using multi-exponential fits to decay curves is plotted in Fig. 4d. The LT also exhibits a decrease with temperature, but the decrease is slower and T50% occurs at 500 K. Overall, the onset of thermal quenching of the Mn^{2+} emission well below room temperature makes this material not suitable for commercial application in LEDs.

Ideally, thermal quenching affects the PL intensity and emission LT in the same manner for a specific quenching mechanism.^{35,41,42} The present observations of excitation wavelength dependent PL quenching and differences in quenching temperature of PL and emission LT suggest a complex quenching behavior. The complex behavior can be explained by the presence of disorder giving rise to Mn^{2+} ions with differences in local coordination affecting both the emission wavelength and quenching temperature.⁴⁴ The $[\text{Ca}(\text{N},\text{O})_7]$ polyhedron in $\text{Ca-}\alpha\text{-SiAlON}$ possesses three different metal-anion distances.⁴⁵ The mixed anionic coordination of $\alpha\text{-SiAlON}$ and the size difference of dopant ions with Ca ions, can give rise to variations in the local Mn^{2+} coordination and thus crystal field variations among different Mn^{2+} ions occupied in polyhedral sites. This also can explain the monotonous PL quenching above 25 K accompanied with PL blue shift as the longer wavelength Mn^{2+} PL emission has a smaller activation energy for thermal quenching and is quenched at lower temperatures. This is consistent with the configuration coordinate diagram crossover model showing lower activation energy for red-shifted emission transitions (ESI,† Fig. S8).^{39,40} Accordingly, the PL spectrum at low temperature consists of multiple Mn^{2+} emissions arising from several $[\text{Mn}(\text{N},\text{O})_7]$ sites with differences in (N,O) coordination. Upon increasing the temperature, the low energy (long wavelength) emission contributions in PL spectrum systematically decrease. The near exponential decay curve profile at 4.2 K suggests that the crystal field variations are small and that the PL is efficient at 4.2 K. As temperature rises, the quenching of lower activation energy emission induces a progressive nonlinearity in decay curves (Fig. 4c). The presence of multiple Mn^{2+} emissions arising from several different sites also gives rise to a broader Mn^{2+} PL profile even at 4.2 K. The temperature induced quenching of longer wavelength emissions explains the observed limited thermal broadening in overall PL profile (Fig. 4b) and the significant blue shift of the emission band maximum. To confirm the presence of multiple sites, PLE spectra were recorded at 4.2 K monitoring different emission regions (ESI,† Fig. S9). The PLE spectra revealed small changes as a function of monitoring wavelengths, specifically for the

sharp excitation bands at around 440 nm. Nevertheless, the overlap in the broad Mn^{2+} emission bands makes it difficult to individually isolate each component and do true site selective spectroscopy.

The results and analysis presented above clearly indicate that the Mn^{2+} ions in $\text{Ca-}\alpha\text{-SiAlON}$ occupy the $[\text{Ca}(\text{N},\text{O})_7]$ polyhedral site with disorder in the (N,O) coordination leading to crystal field variations explaining the broad deep-red PL and complex temperature behavior. Surprisingly, in previous studies on Mn^{2+} activated $\text{Ca-}\alpha\text{-SiAlON}$, many reports proposed narrow-band orange Mn^{2+} emission centered at around 600 nm.^{17–19} As our results showed completely different observations, we were intrigued by the literature reports and therefore carefully investigated the cause for the reported orange Mn^{2+} PL in $\text{Ca-}\alpha\text{-SiAlON}$. We have also experienced presence of similar orange PL in several oxynitride/nitride compositions singly doped with Mn^{2+} ions, specifically in Al-based compositions. Careful inspection reveals that the peak position and the relatively narrow band profile of these orange emissions show close similarity to that of the Mn^{2+} emission of AlN:Mn . In AlN , Mn^{2+} ions have tetrahedral coordination, which together with high Mn–N covalency related shift (Nephelauxetic effect), leads narrow-band orange PL at around 600 nm.^{6–8} Interestingly, the previous reports on $\text{Ca-}\alpha\text{-SiAlON:Mn}^{2+}$ clearly showed the presence of AlN impurity phase in the samples,^{17–19} which may result from either an excess AlN contents or incomplete synthesis (reaction temperature too low or reaction time too short). While optimizing the synthesis conditions for $\text{Ca-}\alpha\text{-SiAlON}$, we also observed a similar but very weak emission at orange region in incompletely synthesized sample.

To provide further support for the assignment of the narrow orange emission to Mn^{2+} emission in impurity phase AlN:Mn^{2+} , single phase AlN:Mn^{2+} and Al-based oxynitrides were

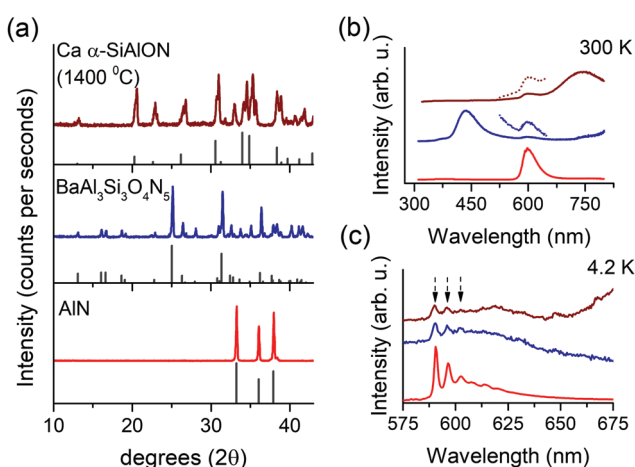


Fig. 5 XRD patterns of $\text{Ca-}\alpha\text{-SiAlON}$ (1400 °C), $\text{BaAl}_3\text{Si}_3\text{O}_4\text{N}_5$ and AlN (a), Mn^{2+} PL in respective samples at 300 K (b) and at 4.2 K (c) under 275 nm excitation. In (a), the gray colored patterns represent reference diffraction patterns ($\lambda_{\text{K}\alpha} = 1.5401 \text{ \AA}$). The samples are identified using line colors as indexed in (a). In (c), the dotted arrows point position of vibronic side bands.



synthesized. Fig. 5a shows the XRD patterns of Mn-doped AlN, BaSi₃Al₃O₄N₅ (synthesized at 1650 °C) and an incompletely synthesized Ca- α -SiAlON (synthesized at 1400 °C). Both AlN and BaSi₃Al₃O₄N₅ exhibit good phase purity. BaSi₃Al₃O₄N₅ usually accompany a small amount of oxide impurity (BaSi₂Al₂O₈), but its influence on the PL properties is negligible.^{30,46} No AlN impurity was detected in the BaSi₃Al₃O₄N₅ PXRD pattern indicating that an AlN impurity phase is present in less than a few %, the detection limit of impurity phases in PXRD. Especially impurity phases of light elements (low X-ray scattering or atomic form factor) are harder to detect. Ca- α -SiAlON (synthesized at 1400 °C) revealed mixed compound with several unidentified impurity phases due to incomplete sintering reaction. The room temperature (300 K) PL properties of these samples are presented in Fig. 5b. The single phase AlN:Mn sample shows the typical bright orange PL originating from Mn²⁺ in tetrahedral nitride coordination. In BaSi₃Al₃O₄N₅:Mn, a prominent blue emission at 430 nm (host emission) is observed along with a weak shoulder at 600 nm. A similar weak emission at 600 nm is observed in underreacted Ca- α -SiAlON, accompanied with a broad near-infrared emission (assigned to emission from Mn²⁺ ions). Fig. 5c shows the cryogenic (4.2 K) PL measurements of the orange PL in all three samples. In AlN, the PL exhibits sharp peaks representing vibronic fine structure. This fine structure is well-known and serves as a fingerprint for the presence of AlN:Mn²⁺. An identical fine structure is observed for orange PL of other two samples. The vibronic fine-structure reflects coupling with host lattice vibrations, similar to those observed in Raman spectra.⁴⁷ The observation of identical fine-structure in the orange emission observed for Ca- α -SiAlON:Mn²⁺ and BaSi₃Al₃O₄N₅:Mn²⁺ suggests that the orange PL is indeed originating from same compound, *i.e.* AlN:Mn, present as an impurity phase in these Al-based oxynitrides. Indeed, it can be expected that the bright orange emission from AlN:Mn can be observed in other Al-based oxynitrides because of the high efficiency and because AlN phases can go easily undetected in PXRD, especially in compositions with heavier elements such as Ba which have larger X-ray scattering cross-sections. Cryogenic measurements are a powerful tool to verify the presence of AlN:Mn²⁺ because of the characteristic fine structure in the low temperature emission spectrum.

As discussed above the PXRD pattern of BaSi₃Al₃O₄N₅:Mn did not reveal detectable presence of AlN traces, but still in PL, although weak, the orange emission could be observed. This is explained by the bright luminescence of AlN:Mn. As a result, in Mn²⁺-doped compounds having weak or no emission, a presence of AlN impurity, even in small amount, can lead prominent orange PL, which can easily be misinterpreted and attributed to the primary compound. Such effect has previously been reported for Eu²⁺ PL in CaZnOS, where the emission was arising from impurity phase CaS:Eu²⁺ and the pure CaZnO-S:Eu²⁺ is non-luminescent.⁴⁸ This effect can be further enhanced by solubility differences. Mn²⁺ is a large cation with respect to Al or Si, and in nitride tetrahedral coordination, its solubility is small. Cherepy *et al.* proposed that about 0.6%

Mn²⁺ ions can be uniformly incorporated in AlN lattice (Al–N bond length about 0.18 nm).⁸ In Ca- α -SiAlON or other low field-strength metal ions containing compositions, the [(Al/Si)N₄] tetrahedron is even smaller (Al/Si–N bond length about 0.17 nm) and thus it is more difficult for Mn²⁺ ions to substitute on tetrahedral sites. In absence of appropriate doping sites, such as Mg, Zn, Ca, *etc.*, Mn²⁺ doping and/or emission is highly inefficient in several compounds, such as BaSi₃Al₃O₄N₅ (Ba²⁺ site is too large for Mn²⁺ ions). In lower purity BaSi₃Al₃O₄N₅ compound, the intensity of orange PL is even higher over that in Fig. 5b. We have observed prominent orange Mn²⁺ PL in the Ba-stabilized composition (known as Ba-s-phase) BaAlSi₅O₂N₇, space group *Imm2*⁴⁹ and in SrAl₂Si₂O₂N₃, exhibiting AlN as impurity phase (ESI,† Fig. S10). All these samples show identical PL vibronic fine structure to that of AlN and their PL decay kinetics is also similar.

Another reason to doubt the assignment of orange PL to Mn²⁺ in Ca- α -SiAlON (or respective other oxynitride compounds) is its inability of getting sensitized when codoped with sensitizer ions, such as Eu²⁺. Ni *et al.* and Zhang *et al.* investigated the Eu²⁺–Mn²⁺ codoped Ca- α -SiAlON.^{19,20} Ni *et al.* showed the presence of Mn²⁺ narrow-band orange PL at 600 nm in singly doped Ca- α -SiAlON, but in Eu²⁺–Mn²⁺ codoped sample, only Eu²⁺ emission was observed. We previously observed similar results in Ba-s-phase, where the Mn²⁺ singly doped sample exhibits prominent 600 nm emission, but in codoped sample, only Eu²⁺ emission appears (ESI,† Fig. S10 and S11). This is due to the fact that the 600 nm emission is coming from impurity AlN phase, thus preventing any short range non-radiative sensitization interaction with donor ions (Eu²⁺) incorporated in primary compound. Zhang *et al.*²⁰ showed quenching of Eu²⁺ PL with increase in Mn²⁺ codoping in Ca- α -SiAlON, but no sensitized Mn²⁺ emission was reported. As the donor emission exhibited quenching upon Mn²⁺ codoping, it is evident that the energy transfer is taking place. In the present investigation, we showed that Mn²⁺ ions exhibit broad deep-red PL in Ca- α -SiAlON, thus it is expected that the sensitized luminescence, if present should be observed at deep-red spectral region in the codoped samples.

To investigate the possibility of sensitizing the Mn²⁺ emission in Ca- α -SiAlON we co-doped with different sensitizers. Fig. 6a shows the PL properties of Eu²⁺ singly doped and Eu²⁺–Mn²⁺ codoped Ca- α -SiAlON. The Eu²⁺ singly doped sample shows bright yellow emission and the PLE exhibits typical Eu²⁺ broad-band profile. In Eu²⁺–Mn²⁺ codoped sample, the Eu²⁺ PL intensity decreases, but a prominent Mn²⁺ sensitized luminescence is missing. The deep-red PL region of codoped sample indeed shows a small increase in intensity as can be seen from the normalized PL spectra in Fig. 6b. The intensity further improves at cryogenic temperature (4.2 K) PL measurements, as the Mn²⁺ emission is partially thermally quenched at 300 K. Still, the sensitized Mn²⁺ emission intensity is fairly weak. Similar small elevation of deep-red region PL in Eu²⁺–Mn²⁺ codoped Ca- α -SiAlON could be witnessed in earlier work of Zhang *et al.*,²⁰ but its weak, non-prominent nature at room-temperature might have left it unnoticed. The donor (Eu²⁺) PL decay curves are presented in



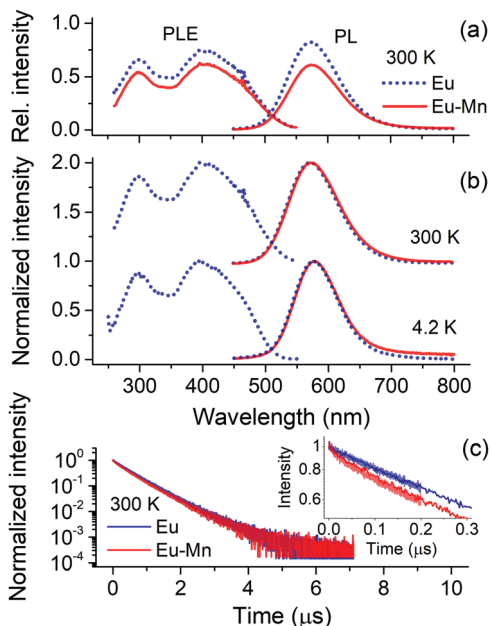


Fig. 6 PL–PLE spectra of Eu^{2+} singly doped and Eu^{2+} – Mn^{2+} codoped $\text{Ca-}\alpha\text{-SiAlON}$ (a); normalized spectra at 300 K and 4.2 K (b); and Eu^{2+} PL decay curves monitored at 575 nm (c). Inset of (c) shows enlarged view of normal decay curves (channel width 2.4 ns) in combination with high-resolution decay curves (channel width 0.048 ns, broader translucent lines). The doping concentration for Eu^{2+} was 0.5 at% and for Mn^{2+} was 10 at%. The excitation and emission wavelengths for PL and PLE measurements were 412 nm and 575 nm, respectively.

Fig. 6c, shows a slightly faster decay in codoped sample, confirming the presence of Eu^{2+} – Mn^{2+} non-radiative energy transfer. The decay

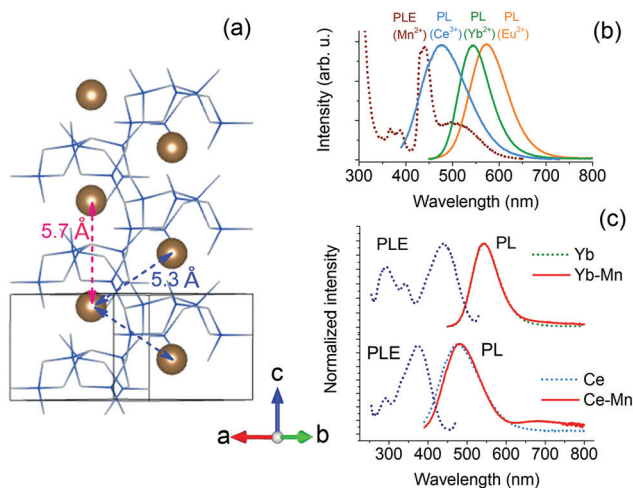


Fig. 7 $\text{Ca-}\alpha\text{-SiAlON}$ crystal structure depicting Ca-Ca separation (a); spectral overlap of Mn^{2+} absorption (dotted line) with emissions (solid lines) of Eu^{2+} , Yb^{2+} and Ce^{3+} donor ions (b); and normalized PL–PLE spectra of Yb^{2+} and Ce^{3+} singly doped with respective Mn^{2+} codoped $\text{Ca-}\alpha\text{-SiAlON}$ at 300 K (c). The doping concentration for Yb^{2+} and Ce^{3+} was 0.5 at%, and for Mn^{2+} was 10 at%. The excitation and emission wavelengths for PL and PLE measurements were 412 nm and 545 nm, respectively for Yb^{2+} -doped samples, and 375 nm and 495 nm for Ce^{3+} -doped samples, respectively.

time decreases from 586 ns in Eu^{2+} singly doped $\text{Ca-}\alpha\text{-SiAlON}$ to 556 ns in Eu^{2+} – Mn^{2+} codoped $\text{Ca-}\alpha\text{-SiAlON}$. The inset shows high-resolution decay curves of the initial decay kinetics, suggesting absence of any fast energy transfer quenching, typically observed for Eu^{2+} – Mn^{2+} energy transfer by exchange interactions.³⁵ Based on the donor decay analysis, the energy transfer efficiency is about 4.7% for 10 at% Mn^{2+} codoping in 0.5 at% Eu^{2+} -doped $\text{Ca-}\alpha\text{-SiAlON}$.

The results show that sensitization of Mn^{2+} emission by Eu^{2+} ions is inefficient in $\text{Ca-}\alpha\text{-SiAlON}$. The energy transfer interaction between Eu^{2+} and Mn^{2+} is governed by short-range interactions, such as exchange (or dipole–quadrupole) interaction.⁵⁰ We have recently shown that exchange interaction dominates the sensitization mechanism in $\text{Ba}_2\text{MgSi}_2\text{O}_7$ by carefully analyzing the high-resolution donor decay kinetics.³⁵ Accordingly, a fast nanosecond sensitization occurs due to exchange mediated energy transfer between nearest neighbor ($< 5 \text{ \AA}$) Eu^{2+} – Mn^{2+} ion pairs, and the transfer rate significant decreases for the next nearest neighbors ($> 5 \text{ \AA}$) ions following exponential distance dependence. As both Eu^{2+} and Mn^{2+} ions occupy Ca^{2+} site in $\text{Ca-}\alpha\text{-SiAlON}$, the Ca-Ca separation provides the nearest-possible neighboring distance. Fig. 7a presents the $\text{Ca-}\alpha\text{-SiAlON}$ structure, showing the Ca-Ca inter-ionic separation. Accordingly, the closest Ca-Ca separation is about 5.3 \AA , and the next nearest neighbor lie at 5.7 \AA along c -axis to the unit cell. This suggests that the $\text{Ca-}\alpha\text{-SiAlON}$ is a dilute crystal structure with nearest neighbor distances too large for efficient exchange interactions. Another reason for inefficient sensitization is the poor spectral overlap between Eu^{2+} emission with Mn^{2+} absorption in $\text{Ca-}\alpha\text{-SiAlON}$ (Fig. 7b). Fig. 7b also shows the emission spectra of Yb^{2+} and Ce^{3+} , which possess better spectral overlap with Mn^{2+} absorption in $\text{Ca-}\alpha\text{-SiAlON}$ and can be expected to improve Mn^{2+} sensitization. Fig. 7c shows the normalized PL–PLE spectra of 0.5 at% Yb^{2+} and Ce^{3+} singly doped $\text{Ca-}\alpha\text{-SiAlON}$ together with 10 at% Mn^{2+} codoped samples. As expected, the sensitized Mn^{2+} emission intensity slightly improved for Yb^{2+} donor ion sample compared to Eu^{2+} and even stronger improvement is observed in Ce^{3+} donor ion codoped $\text{Ca-}\alpha\text{-SiAlON}$. In Ce^{3+} – Mn^{2+} codoped $\text{Ca-}\alpha\text{-SiAlON}$, the sensitized Mn^{2+} emission can distinctly be observed at 300 K. Nevertheless, the sensitized emission intensity is still weak compared to donor emission even at 10 at% Mn^{2+} codoping and having resonant spectral overlap. This confirms our conclusion that a large inter-ionic separation ($> 5 \text{ \AA}$) between donor– Mn^{2+} ions is primarily responsible for inefficient Mn^{2+} sensitization in $\text{Ca-}\alpha\text{-SiAlON}$.

D Conclusions

We have presented an in-depth study of the luminescence of Mn^{2+} in $\text{Ca-}\alpha\text{-SiAlON}$. At low temperatures deep red/NIR emission is observed between 600 and 900 nm. The emission is assigned to ${}^4\text{T}_1 \rightarrow {}^6\text{A}_1$ emission for Mn^{2+} substituted in the $[\text{Ca}(\text{N},\text{O})_7]$ polyhedron. Deep red emission is explained by the strong nephelauxetic effect in nitride coordination, shifting



the emission to longer wavelengths than typically observed for Mn²⁺ d–d emission.

The emission shows unusual properties: the bandwidth is large (FWHM about 200 nm), thermal quenching occurs gradually over a wide temperature range (instead of the usual sharp drop) and the band maximum shows a remarkably large 70 nm blue shift upon raising the temperature. All these observations are explained by disorder in the local O–N coordination around Mn²⁺ in the polyhedron. This gives rise to variations in the crystal field. Mn²⁺ ions experiencing stronger crystal fields show longer wavelength emission with lower quenching temperatures. The role of crystal field inhomogeneity is further confirmed by the non-exponential emission decay curve at 4.2 K, which becomes increasingly non-exponential at higher temperatures. Interestingly, the present observation of deep red emission is different from previous reports on narrow band orange emission for Mn²⁺ in Ca- α -SiAlON. Based on careful analysis, including comparison of vibrational fine structure in low temperature spectra, it is concluded that the orange emission in fact originates from a small amount of AlN:Mn²⁺ impurity phase.

The absorption strength of the spin- and parity-forbidden d–d transitions of Mn²⁺ is low and successful application as a phosphor requires combination with a sensitizer. Sensitization of the Mn²⁺ emission was attempted by co-doping with Eu²⁺, Yb²⁺ and Ce³⁺, all having strong parity allowed f–d transitions. Sensitization was observed but proved to be inefficient as the nearest sensitizer–Mn²⁺ distance is over 5 Å, too large for efficient energy transfer *via* exchange interaction.

The new insights show that efficient deep red emission from a Mn²⁺-doped (oxy)nitride is possible for Mn²⁺ in polyhedral coordination with a crystal field splitting larger than for tetrahedral coordination. Thermal quenching is an issue and needs to be prevented by limiting excited state relaxation. To allow for sensitization the Mn²⁺ ions need to be incorporated in a host lattice that allows for short separation (<5 Å) between sensitizer and Mn²⁺ as exchange interaction is required for efficient energy transfer. Applying these design rules will contribute to the discovery of efficient deep red or NIR phosphors based on Mn²⁺ d–d emission in (oxy)nitrides.

Author contributions

ADS and AM conceptualized the original research idea. ADS and AJB carried out experimental work. After formal analysis and discussion with all, ADS wrote the original draft and all authors contributed in revision and editing of final draft.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

Financial support from Nichia Corporation (Japan) is gratefully acknowledged.

References

- 1 T. Takeda, R.-J. Xie, T. Suehiro and N. Hirosaki, *Prog. Solid State Chem.*, 2018, **51**, 41.
- 2 K. Uheda, N. Hirosaki and H. Yamamoto, *Phys. Status Solidi*, 2006, **203**, 2712.
- 3 K. Uheda, *et al.*, *Electrochem. Solid-State Lett.*, 2006, **9**, H22.
- 4 H. A. Höpfe, H. Lutz, P. Morys, W. Schnick and A. Seilmeier, *J. Phys. Chem. Solids*, 2000, **61**, 2001.
- 5 R. Mueller-Mach, G. Mueller, M. R. Krames, H. A. Höpfe, F. Stadler, W. Schnick, T. Jüstel and P. Schmidt, *Phys. Status Solidi*, 2005, **202**, 1727.
- 6 G. J. Hoerder, M. Seifald, D. Baumann, T. Schröder, S. Peschke, P. C. Schmid, T. Tyborsky, P. Pust, I. Stoll, M. Bergler, C. Patzig, S. Reibaus, M. Krause, L. Berthold, T. Höche, D. Johrendt and H. Huppertz, *Nat. Commun.*, 2019, **10**, 1824.
- 7 P. Pust, V. Weiler, C. Hecht, A. Tücks, A. S. Wochnik, A.-K. Henß, D. Wiechert, C. Scheu, P. J. Schmidt and W. Schnick, *Nat. Mater.*, 2014, **13**, 891.
- 8 N. J. Cherepy, S. A. Payne, N. M. Harvey, D. Åberg, Z. M. Seeley, K. S. Holliday, I. C. tran, F. Zhou, H. Paul Martinez, J. M. Demeyer, A. D. Drobshoff, A. M. Srivastava, S. J. Camardello, H. A. Comanzo, D. L. Schlagel and T. A. Lograsso, *Opt. Mater.*, 2016, **54**, 14.
- 9 X.-J. Wang, R.-J. Xie, B. Dierre, T. Takeda, T. Suehiro, N. Hirosaki, T. Sekiguchi, H. Li and Z. Sun, *Dalton Trans.*, 2014, **43**, 6120.
- 10 J. Xu, N. Cherepy, J. Ueda and S. Tanabe, *Mater. Lett.*, 2017, **206**, 175.
- 11 R.-J. Xie, N. Hirosaki, X.-J. Liu, T. Takeda and H.-L. Li, *Appl. Phys. Lett.*, 2008, **92**, 201905.
- 12 Q.-H. Zhang, J. Wang, C.-W. Yeh, W.-C. Ke, R.-S. Liu, J.-K. Tang, M.-B. Xie, H.-B. Liang and Q. Su, *Acta Mater.*, 2010, **58**, 6728.
- 13 M. Sheng, J. Wang, J. Fan, H. Lian, Y. Zhang and J. Lin, *J. Mater. Chem. C*, 2015, **3**, 9306.
- 14 C. J. Duan, W. M. Otten, A. C. A. Delsing and H. T. Hintzen, *J. Solid State Chem.*, 2008, **181**, 751.
- 15 Z. Zhang, A. C. A. Delsing, P. H. L. Notten, J. Zhao, P. Dorenbos and H. T. Hintzen, *ECS J. Solid State Sci. Technol.*, 2013, **2**, R70.
- 16 S. Liu, S. Zhang, N. Mao, Z. Song and Q. Liu, *J. Am. Ceram. Soc.*, 2020, **103**, 6793.
- 17 J. Ni, Q. Liu, J. Wan, G. Liu, Z. Zhou, F. Xu, X. Zeng and R.-J. Xie, *J. Lumin.*, 2018, **202**, 514.
- 18 J. Ni, Q. Liu, Z. Zhou and G. Liu, *RSC Adv.*, 2017, **7**, 42211.
- 19 J. Ni, Z. Z. Zhou, X. K. Xu, Q. Liu, F. R. Shen and L. H. He, *Mod. App. Matl. Sci.*, 2020, **2**, 276.
- 20 Y.-Q. Zhang, X.-J. Liu, Z.-R. Huang, J. Chen and Y. Yang, *J. Lumin.*, 2012, **132**, 2561.
- 21 G. Z. Cao and R. Metselaar, *Chem. Mater.*, 1991, **3**, 242.
- 22 T. Suehiro, N. Hirosaki, R.-J. Xie and M. Mitomo, *Chem. Mater.*, 2005, **17**, 308.
- 23 N. Hirosaki, R.-J. Xie, K. Kimoto, T. Sekiguchi, Y. Yamamoto, T. Suehiro and M. Mitomo, *Appl. Phys. Lett.*, 2005, **86**, 211905.



- 24 S. Li, L. Wang, D. Tang, Y. Cho, X. Liu, X. Zhou, L. Lu, L. Zhang, T. Takeda, N. Hirosaki and R.-J. Xie, *Chem. Mater.*, 2018, **30**, 494.
- 25 J. W. T. van Rutten, H. T. Hintzen and R. Metselaar, *Ceram. Int.*, 2001, **27**, 461.
- 26 R.-J. Xie, N. Hirosaki, M. Mitomo, Y. Yamamoto, T. Suehiro and K. Sakura, *J. Phys. Chem. B*, 2004, **108**, 12027.
- 27 Y.-Q. Li, N. Hirosaki, R.-J. Xie, J. Li, T. Takeda, Y. Yamamoto and M. Mitomo, *J. Am. Ceram. Soc.*, 2009, **92**, 2738.
- 28 R.-J. Xie, N. Hirosaki, M. Mitomo, K. Uheda, T. Suehiro, X. Xu, Y. Yamamoto and T. Sekiguchi, *J. Phys. Chem. B*, 2005, **109**, 9490.
- 29 M. Mitomo, T. Endo, K. Ueda and M. Komatsu, *EU Pat.*, EP1264873B1, 2011.
- 30 J.-Y. Tang, Y.-M. He, L.-Y. Hao and X. Xu, *J. Mater. Res.*, 2013, **28**, 1598.
- 31 B. J. Adamczyk, M. G. Brik, V. Nagirnyi, I. Romet, D. Michalik, T. Pawlik and M. Sopicka-Lizer, *J. Alloys Compd.*, 2020, **845**, 155468.
- 32 S. Okamoto and H. Yamamoto, *J. Electrochem. Soc.*, 2011, **158**, J363.
- 33 H.-L. Li, G.-H. Zhou, R.-J. Xie, N. Hirosaki, X.-J. Wang and Z. Sun, *J. Solid State Chem.*, 2011, **184**, 1036.
- 34 M. Muller, S. Fischer and T. Jüstel, *RSC Adv.*, 2015, **5**, 67979.
- 35 A. D. Sontakke, A. J. van Bunningen, F. T. Rabouw, S. Meijers and A. Meijerink, *J. Phys. Chem. C*, 2020, **124**, 13902.
- 36 M. de Jong, L. Seijo, A. Meijerink and F. T. Rabouw, *Phys. Chem. Chem. Phys.*, 2015, **17**, 16959.
- 37 T. Wylezich, A. D. Sontakke, V. Castaing, M. Suta, B. Viana, A. Meijerink and N. Kunkel, *Chem. Mater.*, 2019, **31**, 8957.
- 38 J. W. H. van Krevel, J. W. T. van Rutten, H. Mandal, H. T. Hintzen and R. Metselaar, *J. Solid State Chem.*, 2002, **165**, 19.
- 39 K. V. Ivanovskikh, J. N. Ogieglo, A. Zych, C. Ronda and A. Meijerink, *ECS J. Solid State Sci. Technol.*, 2013, **2**, R3148.
- 40 J. Ueda, A. Meijerink, P. Dorenbos, A. J. J. Bos and S. Tanabe, *Phys. Rev. B*, 2017, **95**, 014303.
- 41 T. Sendon, R. J. A. van Dijk-Moes and A. Meijerink, *Light: Sci. Appl.*, 2018, **7**, 8.
- 42 B. Malysa, A. Meijerink and T. Jüstel, *Opt. Mater.*, 2018, **85**, 341.
- 43 Y. Zhang, L. Mei, H. Liu, J.-C. Chang, W.-R. Liu and Z. Huang, *Mater. Chem. Phys.*, 2019, **228**, 215.
- 44 A. D. Sontakke, J.-M. Mouesca, V. Castaing, A. Ferrier, M. Salaun, I. Gautier-Luneau, V. Maurel, A. Ibanez and B. Viana, *Phys. Chem. Chem. Phys.*, 2018, **20**, 23294.
- 45 F. Izumi, M. Mitomo and J. Suzuki, *J. Mater. Sci. Lett.*, 1982, **1**, 533.
- 46 J.-Y. Tang, W.-J. Xie, K. Huang, L.-Y. Hao, X. Xu and R.-J. Xie, *Electrochem. Solid-State Lett.*, 2011, **14**, J45.
- 47 A. R. Evans and D. B. Fitchen, *Phys. Rev. B: Solid State*, 1970, **2**, 1074.
- 48 B. Budde, H. Luo, P. Dorenbos and E. van der Kolk, *Opt. Mater.*, 2017, **69**, 378.
- 49 C. J. Duan, W. M. Otten, A. C. A. Delsing and H. T. Hintzen, *J. Alloys Compd.*, 2008, **461**, 454.
- 50 A. L. N. Stevels and J. M. P. J. Versteegen, *J. Lumin.*, 1976, **14**, 207.

