Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2021, 12, 4425

d All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 28th December 2020 Accepted 27th January 2021

DOI: 10.1039/d0sc07058k

rsc.li/chemical-science

Pressure-induced phosphorescence enhancement and piezochromism of a carbazole-based cyclic trinuclear Cu(ı) complex†

Mo Xie, D^a Xiao-Ru Chen, Kun Wu, D^a Zhou Lu, D^a Kai Wang, D^c Nan Li, Rong-Jia Wei, D^a Shun-Ze Zhan, D^b Guo-Hong Ning, D*^a Bo Zou *Cand Dan Li *Cand

Interest in piezochromic luminescence has increased in recent decades, even though it is mostly limited to pure organic compounds and fluorescence. In this work, a Cu_3Pz_3 (Cu_3 , Pz: pyrazolate) cyclic trinuclear complex (CTC) with two different crystalline polymorphs, namely 1a and 1b, was synthesized. The CTC consists of two functional moieties: carbazole (Cz) chromophore and Cu_3 units. In crystals of 1a, discrete $Cz-Cu_3-Cu_3-Cz$ stacking was found, showing abnormal pressure-induced phosphorescence enhancement (PIPE), which was 12 times stronger at 2.23 GPa compared to under ambient conditions. This novel observation is ascribed to cooperation between heavy-atom effects (*i.e.*, from Cu atoms) and metal–ligand charge-transfer promotion. The infinite $\pi-\pi$ stacking of Cz motifs was observed in 1b and it exhibited good piezochromism as the pressure increased. This work demonstrates a new concept in the design of piezochromic materials to achieve PIPE via combining organic chromophores and metal–organic phosphorescence emitters.

Introduction

Piezochromic luminescent compounds are a class of stimuliresponsive materials^{1,2} which exhibit significant emission colour changes in response to grinding, pressing and stretching, and they show great potential in a wide range of applications, including pressure sensors, optical recording, and memory.^{3–10} Recent studies revealed that chromic mechanisms of such materials are related to pressure-controllable molecular switches,^{11–13} phase transition,^{14,15} conformational transformation,^{16,17} excited state transformation,¹⁸ and aggregation-

^aCollege of Chemistry and Materials Science, Guangdong Provincial Key Laboratory of Functional Supramolecular Coordination Materials and Applications, Jinan University, Guangzhou, Guangdong 510632, People's Republic of China. E-mail: guohongning@jnu.edu.cn; danli@jnu.edu.cn

induced emission (AIE) effect.^{19,20} To date, the molecular design and material selection for piezochromism are mostly focused on organic molecules.^{21–25} Because of the weak spinorbital coupling and a long triplet-state lifetime, the pure organic molecules hardly show phosphorescence at room temperature (rt).^{26,27} Thus, most of piezochromic luminescent materials display a pressure-induced fluorescence change at rt (*e.g.*, quenched or enhanced intensity and bathochromic/hypsochromic shifts),^{5,12,20} whereas pressure-induced phosphorescence enhancement (PIPE) materials are highly challenging and still remain unexplored.


Cyclic trinuclear complexes (CTCs) with d10 metals are well known for their characteristic $M_3N_xC_{6-x}$ (M = Au, Ag, or Cu; x =0, 3, or 6) nine-membered ring and corresponding π -acidity/ basicity, and metal-metal interactions (metallophilicity) which play essential roles in photoluminescence (PL) and other properties. 28,29 In cooperation with other supramolecular interactions (non-covalent interactions),30 such stimuli-responsive luminescence has often been reported in the CTC family, including piezochromism,31 thermochromism,32-34 solvatochromism, and concentration luminochromism.35 In previous studies, phosphorescence of organic chromophores could be triggered at cryogenic temperatures or even at rt, after forming CTC/organic adducts or if directly serving as ligands. 28,36,37 Such luminescence, termed "metal-sensitized phosphorescence", is attributed to the enhanced intersystem crossing (ISC) rate from singlet excited states to triplet states mediated by an external heavy-atom effect (e.g., Au, Ag, Cu and Hg).38,39 In this way, it is proposed that

^bDepartment of Chemistry, Shantou University, Shantou, Guangdong 515063, People's Republic of China

^{&#}x27;State Key Laboratory of Superhard Materials, Jilin University, Changchun 130012, People's Republic of China. E-mail: zoubo@jlu.edu.cn

 $[\]dagger$ Electronic supplementary information (ESI) available: Experimental and calculation details; general characterization data, including IR, PXRD, and TGA; crystal data and structure refinement parameters; UV-vis spectra; varied-temperature solid-state emission spectra; detailed photophysical data and proposed Jablonski diagrams; linear relationships; detailed TDDFT results; and pressure-dependent simulation results. CCDC 2043666–2043668. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0sc07058k

[‡] Present address: Department of Chemistry, University of North Texas, Denton, Texas 76203, USA.

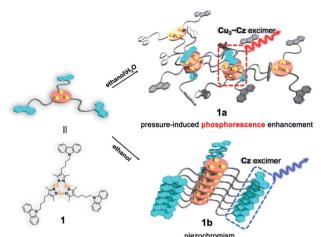

Scheme 1 A schematic representation showing the molecular stacking of two crystalline polymorphs 1a and 1b, and the formation of the Cu_3Pz_3 CTC $Cz-Cu_3-Cu_3-Cz$ excimer and carbazole (Cz) excimer with an increase in pressure.

the external isotropic pressure can enforce the interactions between CTCs and organic chromophores, resulting in alteration of electronic structures of the emission centre and triggering the PIPE. As far as is known, investigations of the luminescence behaviour of such organic chromophore-CTC adducts under high pressure have rarely been reported.

In this work, a carbazole-based Cu(I) CTC (1) was designed by linking classic organic chromophore carbazole⁴⁰ (Cz) and

Cu₃Pz₃ CTCs (Cu₃ Pz: pyrazolate) with a non-conjugated flexible *n*-butyl chain. Two crystalline polymorphs, denoted as **1a** and **1b**, are obtained and exhibit two different stacking models leading to the formation of [Cz–Cu₃–Cu₃–Cz] excimers and Cz excimer/aggregator, respectively (Scheme 1). Therefore, metalsensitized phosphorescence and the ligand-dominated luminescence are observed for **1a** and **1b**, respectively. Furthermore, **1a** shows an unprecedented PIPE phenomenon, which has never been reported in piezochromic materials, and **1b** exhibits conventional carbazole characteristic piezochromic luminescence with a good linear relationship of intensity *versus* external pressure.

Results and discussion

The yellow block-shaped crystals of ${\bf 1a}$, or colourless fibrous crystals of ${\bf 1b}$ were obtained by mixing 9-(4-(3,5-dimethyl-1*H*-pyrazol-4-yl)butyl)-carbazole ligand (*HL*) and Cu₂O in anhydrous ethanol or ethanol/water under solvothermal conditions (see ESI† for further details). The freshly synthesized single-crystal samples of ${\bf 1a}$ and ${\bf 1b}$ were characterized by powder X-ray diffraction (PXRD) and infrared (IR) spectroscopy, confirming their phase purity (Fig. S7 and S8, ESI†). The single X-ray crystallographic analysis of ${\bf 1a}$ and ${\bf 1b}$ revealed that both featured the nine-membered Cu₃N₆ CTC composed of Cu₃ units and Cz motifs (Fig. 1a and 2a).

Unlike the conventional sandwich-like ternary adducts (*i.e.*, CTC-organic aromatic-CTC), ^{41,42} unprecedented discrete adducts with a Cz-Cu₃-Cu₃-Cz stacking model were observed in

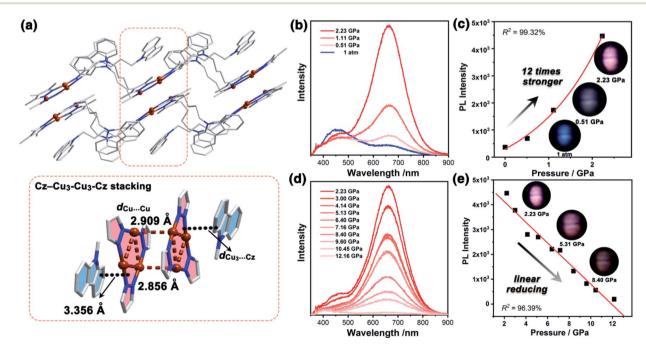


Fig. 1 (a) The crystal packing of $\bf{1a}$ at 100 K, showing discrete $\bf{Cz}-\bf{Cu_3}-\bf{Cz}$ stacking (Cu: brown, C: grey, and N: blue, H atoms are omitted for clarity). Emission spectra of $\bf{1a}$ at a range of external pressures from (b) 1 atm-2.23 GPa and (d) 2.23-12.16 GPa at an excitation wavelength of 355 nm. The curve fitting [function: $y = A_1 \times \exp(-x/t_1) + y_0$, $R^2 = 99.32\%$] and linear fitting [function: $y = A_0 + kx$, $R^2 = 96.39\%$] of pressure and PL intensity for $\bf{1a}$ in pressure ranges of (c) 1 atm-2.23 GPa and (e) 2.23-12.16 GPa (insets of (c) and (e): PL photographs at representative pressure points).

Edge Article

R-2.28 GPa
— R-0.86 GPa
— R-0.00 GPa
— 1 atm

R-2.28GPa
— R-0.86GPa

Fig. 2 The PL spectra and photographs of **1a** in a pressure relief process from 2.28 GPa to 0.00 GPa. The gray line (marked as 1 atm) is the PL spectrum before compression.

600

Wavelength / nm

1000

1a (Fig. 1a). Specifically, two adjacent Cu_3 units adopted a dimer-of-trimer configuration with short intertrimer $d_{Cu\cdots Cu}$ of 2.854 and 2.909 Å, implying that there were strong $Cu\cdots Cu$ interactions between the Cu_3 units. Moreover, one set of Cz groups adducted with the Cu_3 - Cu_3 dimer and the intermolecular plane-to-plane distance between the Cu_3 unit and the Cz group $(d_{Cu_3\cdots Cz})$ was 3.360 Å, which indicated weak π -acid \cdots base interactions (Fig. 1a). It is worth noting that the other Cz groups were randomly arranged and no noticeable interactions between Cu_3 or Cz units were observed (Fig. S10 and S11, ESI†).

1a exhibits a UV-vis absorption profile similar to that of the proligand HL in either CH₂Cl₂ solution or solid state (Fig. S14 and S15, ESI†). The absorption bands of 1a at about 290 and 340 nm can be attributed to ligand-centred (LC) transition. The variable-excitation wavelength PL spectra of 1a at rt were remarkably different from those of the proligand (Fig. S16 and S17, ESI†). As shown in Fig. S18 (ESI†), 1a has low-energy (LE) dominated dual emission bands at about 400 nm (high-energy, HE band) and 680 nm (LE band) with a large LE/HE intensity ratio of 100 ($\lambda_{ex} = 280$ nm). The HE band was consistent with the solid emission of the proligand in both emission energy and band profile, which can be assigned as a LC fluorescence. The LE band intensity was significantly larger compared with that of the proligand, and it remained at a certain strength even under LE excitation (i.e., $\lambda_{ex} = 360$ nm), indicating that the LE band was not limited to the emission of the proligand. Upon increasing the excitation energy, the emission colour changed from blue-white to red (Fig. S18b, ESI†) in the CIE-1931 chromaticity diagram.

Upon cooling to 200 K or a lower temperature, **1a** showed a new broad emission band at 560 nm, whose emission energy was temperature-independent (Fig. S20a, ESI†). To better understand the steady state PL, density functional theory (DFT) and time-dependent density functional theory (TDDFT) calculations were conducted and the calculations based on singlet monomeric **1a** geometry revealed that the low-lying singlet excited states were mainly localized on the **Cz** moieties, until the metal-to-ligand charge transfer (MLCT) character became

dominant in the S14 state (Table S4, ESI†). These results suggested that 1a will produce ¹LC fluorescence upon LE excitation to the S_1 - S_{13} states. By exciting 1a to the S_{14} or higher energy singlet states by increasing excitation energy, the ISC process might be generated by metal copper participation. The Cz-Cu₃-Cu₃-Cz stacking model of 1a is divided into two theoretical models for clarity, denoted as dimer (a) or (b), which contained Cu₃-Cu₃ dimers or Cu₃-Cz adducts, respectively. The lowest single-triplet excited states of both monomer and dimer (a) were localized on the Cz moieties (Table S5, ESI†), which can be assigned as metal-sensitized ligand centred (MSLC) phosphorescence. The charge transfer (3LC/3MLCT) excited state based on the Cu₃-Cz interaction contributed a little (9%) to the triplet emission of dimer (b), suggesting that the copper metal directly participated in the triplet electronic transition rather than just sensitizing the LC emission. Therefore, the LE dual emissions of **1a** can be assigned as the ${}^{3}LC$ of the monomer ($\lambda_{em} = 560 \text{ nm}$) and the domination of the MSLC mixed with the ³MLCT assisted phosphorescence of the Cz-Cu₃-Cu₃-Cz excimer (λ_{em}-= 680 nm). Taking advantage of the Cu_3 -Cz interactions, the heavy atom effects of copper atoms promoted the ISC rate and the generation of low-energy phosphorescence, leading to MSLC phosphorescence dominated emission of 1a. The proposed complete photophysical processes are summarized in Fig. S23 (ESI†).

It is known that pure carbazole possesses excellent piezoluminochromism.40 The unique mixed MSLC/MLCT phosphorescence of Cz-based CTC 1a promoted further study of the PL under high pressure. The isotropic hydrostatic pressure was directly applied via a diamond anvil cell (DAC)43 on crystal samples of 1a (see ESI† for experimental details). At ambient conditions, 1a exhibited LC dominated blue emission, under LE excitation (355 nm). As the external pressure increased, 1a presented constant fluorescence reduction and phosphorescence enhancement. The intensity of the LE phosphorescence showed exponential growth and was greatly increased: 12 times stronger at 2.23 GPa than that at 1 atm (10^{-4} GPa) , whereas the HE emission intensity was slightly weakened, resulting in a remarkable colour change from weak blue to bright pink (Fig. 1b and c). Such PIPE is rare in the piezochromic luminescent materials. When the pressure was greater than 2.23 GPa, the emission intensity decreased linearly (Fig. 1d, e and S24, ESI†). The reduced LE emission and enhanced HE emission recorded during a pressure relief process from 2.28 GPa to 0 GPa (Fig. 2) indicated that the PIPE phenomenon of 1a was reversible. To further explain these results, TDDFT calculations were performed based on the T1 geometry of 1a at 1 atm and 2.5 GPa (Fig. S28-S30, ESI†). Under ambient conditions, the T₁ state was mainly composed of ³LC transition of Cz moieties (79%) and LLCT (ligand-to-ligand charge transfer) transition of Cu_3 -Cz (9%). Pressurizing 1a to 2.5 GPa, the 3 MLCT/ 3 LLCT transition became dominant in the T₁ state (65%) while the percentage of ³LC transition of Cz moieties was reduced to 14%. In addition, when the pressure increased from 1 atm to 2.5 GPa, the Cu contribution in the MLCT increased from 6.46% to 11.75%. These computational results indicated the external pressure strength of the Cu₃-Cz interactions,

Chemical Science

resulting in the increase of the 3 MLCT/ 3 LLCT contribution in the excited state. Combining the crystal structure analysis and the computational results, it can be postulated that the weak LE emission band is attributed to MSLC phosphorescence due to the rather weak ${\bf Cu_3}$ – ${\bf Cz}$ interactions and the negligible Cu contribution to the MLCT state at ambient conditions. When the pressure was increased to 2.23 GPa, the intensity of the LE phosphorescence was greatly enhanced, which could reasonably be attributed to a cooperative effect between heavy-atom effects and MLCT promotion because of the shortening of $d_{{\bf Cu_3}\cdots{\bf Cz}}$ as well as the significant increase of ${\bf Cu_3}$ – ${\bf Cz}$ interactions and Cu contribution in the MLCT (Fig. 4a).

In contrast, the Cu_3 units in 1b packed as a stair-step infinite chain with one pair of weak intertrimer $Cu\cdots Cu$ interactions with a relatively long intermolecular $Cu\cdots Cu$ distance $(d_{Cu\cdots Cu})$

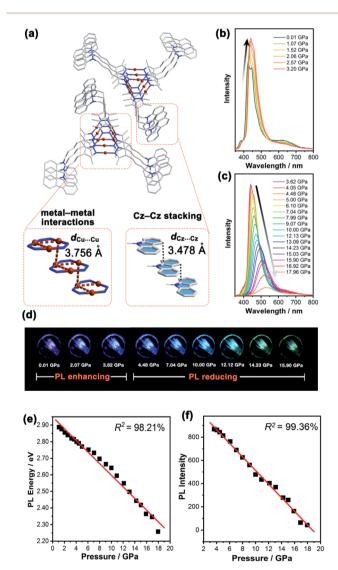


Fig. 3 (a) The crystal packing of 1b at 298 K, showing the infinite chain stacking model of Cz and Cu_3 . The emission spectra of 1b at a range of external pressures from (b) 0.01-3.20 GPa and (c) 3.62-17.96 GPa at an excitation wavelength of 355 nm. (d) PL photographs of the 1b crystal under compression up to 15.90 GPa. Linear fitting of the external pressure and (e) PL energy and (f) PL intensity of 1b.

of 3.756(3) Å at 298 K (Fig. 3a). In addition, the Cz motifs adopted a *I*-type aggregation along the α -axis, whereby the two adjacent Cz groups tightly stacked through π - π interactions with an intermolecular $Cz \cdots Cz$ plane-to-plane distance $(d_{Cz \cdots Cz})$ of about 3.480 Å (Fig. 3a). 1b presented different intensity ratios of higher and lower absorption bands in UV-vis absorption compared with that of 1a, which explained the different crystal colours of 1a and 1b (Fig. S12 and S13, ESI†). In sharp contrast, 1b shows HE dominated dual emission with a much smaller LE/ HE intensity ratio of 1.25 ($\lambda_{ex} = 280$ nm) than that of 1a (Fig. S19a, ESI†). The HE structured bands in the range of 350-500 nm were similar to those for the proligand (Fig. S16 and S17, ESI†) which can be attributed to the LC emission upon LE excitation (i.e., $\lambda_{ex} = 360$ nm). The excitation wavelengthdependent emission colour changes were also found for 1b (Fig. S19b, ESI†). The DFT and TDDFT calculations revealed that the low-lying singlet excited states were Cz localized, confirming the ¹LC feature of the HE emission of **1b**. Both the lowest triplet states of monomeric and dimeric 1b were a 3LC feature (Table S6, ESI†), therefore the LE emission band of 1b can be attributed to the MSLC phosphorescence which experiences the ISC from the ¹MLCT state to the ³MLCT state and the internal conversion (IC) of the triplet state. Such a proposed photophysical mechanism has been commonly observed in other CTC systems.44 Because of the well-ordered J-type aggregation of the Cz motifs, 1b exhibited aggregate/excimer emission with a lower energy in the solid state, which further supported the lower energy broad emission of **1b** compared to that of the proligand. Combining the experimental and computational studies, 1a showed phosphorescence dominated emission, but 1b featured similar emission behaviours to the proligand, revealing that the stacking mode of the organic chromophore in the crystals would be an essential factor for determining the PL properties of the metal-organic complex.

Upon external pressure, the PL of 1b showed a continuous red shift, accompanied by two-step changes including emission enhancement (0.01-3.62 GPa) and emission reduction (3.62-17.96 GPa) under 355 nm excitation (Fig. 3b-d). These observations were similar to the piezoluminochromism of pure Cz (ref. 40) and agreed well with the previously mentioned suggestion for the Cz-centred characteristic luminescence of 1b. Interestingly, both PL energy and intensity (or the integrated area in Fig. S25, ESI†) showed a linear relationship versus the external pressure as shown in Fig. 3e and f, respectively. The emission spectra and photographs taken during the decompression process indicate that the piezoluminochromic phenomena of 1b (Fig. S26, ESI†) was reversible. The pressuredependent structural simulations and frontier molecular orbital (FMO) analysis (Fig. S30–S34, ESI†) of 1b revealed that the $d_{Cz\cdots Cz}$ was the only structural parameter to change consistently with the cell volume change. It is a key factor that influences the overlap of molecular orbitals participating in the PL transition, leading to a continuous bathochromic shift in the PL energy. As the Cz groups were well separated from the Cu₃ moieties with non-conjugated *n*-butyl chains and well packed to form an infinite and column-like Cz aggregator via π - π interactions in the crystals, 1b mainly exhibited the Cz/Cz excimerEdge Article Chemical Science

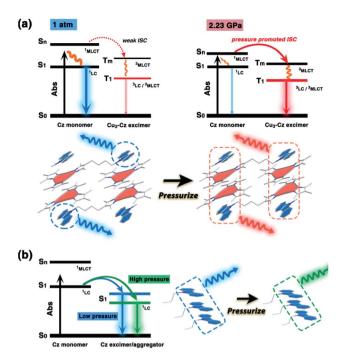


Fig. 4 A schematic diagram of the (a) pressure-induced phosphorescence enhancement of **1a**, and (b) the piezochromism of **1b**. The dominant luminescent components are highlighted.

based luminescence and the contribution of MLCT to the PL were negligible (Fig. 4b), and which are not favoured for d¹⁰-metal CTCs.³⁹

Conclusions

In summary, a new piezochromic material, carbazole-based Cu(1) CTCs, consisting of a carbazole chromophore and Cu₃Pz₃ functional moieties linked by a non-conjugated alkyl chain, was designed. Significant stacking conformations were observed in the two crystalline polymorphs of 1a and 1b: discrete Cu_3 -Cz adducts via π -acid...base interactions were found in 1a, whereas the infinite π - π stacking of Cz groups and a stair-step infinite chain of Cu₃ motifs were obtained in 1b. Like pure carbazole molecules, upon increasing the external pressure, the emission maximum of 1b gradually red-shifted and the intensity of the fluorescence band slightly increased before gradually decreasing. However, the unprecedented phenomenon of the pressure-induced phosphorescence enhancement (PIPE) of 1a was discovered, which was a rare case in the field of piezochromic luminescence. Theoretical and experimental investigations illustrated that the increase of the LE phosphorescence band intensity originated from the Cu₃-Cz excimer in 1a. External heavy atom effects induced MSLC phosphorescence and then promoted MLCT events from the Cu₃ unit to the Cz groups cooperatively contributed to the enhancement of the LE phosphorescence band from 1 atm to 2.5 GPa. These studies demonstrated a novel strategy for designing a new class of piezochromic materials with PIPE properties via the combination of external heavy atom effects

and MLCT promotion. The excellent responses to pressure of **1a** and **1b** make them promising materials for use as pressure sensors or in pressure detection.

Experimental section

Materials

All starting materials were purchased from commercial sources and used as received without further purification. Detailed characterization methods are included in the ESI.†

Synthesis of the 9-(4-(3,5-dimethyl-1H-pyrazol-4-yl)butyl)carbazole ligand (HL). Carbazole (10.32 g) was dissolved in 100 mL of toluene, and the solution was added to 1,4-dibromobutane (118.2 g, 547.4 mmol) and tetrabutylammonium bromide (TBAB, 2 g) in a 500 mL round bottom flask, and then 100 mL of 50% sodium hydroxide solution was added into the mixed solution, and the stirring was continued at 45 °C for 24 h. The mixed solution was extracted with dichloromethane, the extraction solvent was then steamed and placed under a fume hood and allowed to volatilize for a week. After evaporation to dryness, the blue solid obtained was separated and purified by column chromatography to obtain a large amount of a white solid, which was intermediate HL-1: 9-(4-bromobutyl)-9Hcarbazole with a yield of about 86%. ¹H-NMR (400 MHz, CD₂Cl₂) δ 8.16 (d, J = 7.8 Hz, 1H), 7.50 (m, 2H), 7.28 (dd, J = 7.9, 6.8 Hz, 1H), 4.39 (t, J = 7.2 Hz, 1H), 3.44 (t, J = 6.5 Hz, 1H), 2.07 (m, 1H), 1.95 (m, 1H) ppm. 13 C-NMR (400 MHz, CD₂Cl₂) δ 140.3, 125.7, 122.8, 120.3, 118.9, 108.7, 42.2, 33.4, 30.4, 27.6 ppm. Elemental analysis for C₁₆H₁₆BrN, calcd (%): C 63.59, H 5.34, N 4.62; found (%): C 64.07, H 5.63, N 4.58.

The eluent selected was dichloromethane: petroleum ether (1:8). Next K₂CO₃ (80 mol, 11.04 g), acetylacetone (60 mmol, 6 mL), and a small amount of 18-crown-6 was added to a threenecked round bottom flask containing 100 mL of acetone. Then 1-bromobutyl 4-oxazole (20 mmol, 6.038 g) was dissolved in 60 mL of acetone and placed in a dropping funnel and attached to a three-necked flask. After installing the device, nitrogen gas was added and the mixture was stirred at rt for 30 min. After 30 min, the temperature was raised to 50 °C, and the 1-bromobutyl 4-oxazole solution in the dropping funnel was gradually added dropwise to the three-necked flask, and the mixture was heated to reflux, and the nitrogen was left flowing for 17 h. After the reaction was completed, distilled water was added, and the mixture was extracted with a dichloromethane solution, and then steamed, and purified by column chromatography. The eluent selected was dichloromethane: petroleum ether (1:10) and colorless needle-like crystals were obtained, which was the intermediate *HL-2*: 3-(4-(9*H*-carbazol-9-yl)butyl) pentane-2,4-dione with a yield of about 51%. ¹H-NMR (400 MHz, CD_2Cl_2) δ 8.13 (d, J = 7.8 Hz, 1H), 7.48 (m, 2H), 7.26 (dd, J= 7.4, 6.9 Hz, 1H, 4.35 (t, J = 7.2 Hz, 1H), 3.58 (t, J = 7.1 Hz, 1H),2.12 (m, 3H), 1.92 (m, 1H), 1.84 (m, 1H), 1.35 (m, 1H) ppm. ¹³C-NMR (400 MHz, CD_2Cl_2) δ 204.0, 140.4, 125.6, 122.7, 120.2, 118.8, 108.7, 68.1, 42.7, 29.2, 28.8, 27.8, 25.3 ppm. Elemental analysis for C21H23NO2, calcd (%): C78.47, H7.21, N4.36; found (%): C 78.67, H 7.40, N 4.37.

The diketone intermediate was added to a flask containing hydrazine hydrate (80%, 14 mL), ethanol (100 mL), and kept at 70 °C for 15 h, and the ethanol evaporated to give a yellow oil. After freezing in a refrigerator for one week, the yellow oil was taken out, and a white solid was observed. After washing with a diethyl ether solution, it was filtered and dried to give a product *HL* [9-(4-(3,5-dimethyl-1*H*-pyrazol-4-yl)butyl)-9*H*carbazole] with a yield of about 39%. ¹H-NMR (400 MHz, CD_2Cl_2) δ 8.13 (d, J = 7.8 Hz, 1H), 7.50 (m, 2H), 7.25 (dd, J = 7.9, 6.7, 1H), 4.35 (t, J = 7.2 Hz, 1H), 2.38 (t, J = 7.6 Hz, 1H), 2.13 (s, 3H), 1.90 (m, 1H), 1.56 (m, 1H) ppm. ¹³C-NMR (400 MHz, CD_2Cl_2) δ 141.8, 140.4, 125.6, 122.7, 120.2, 118.7, 115.0, 108.7, 43.0, 28.7, 28.2, 22.8, 10.6 ppm. IR spectrum (KBr, cm⁻¹): 3203 (w), 3147 (w), 3089 (w), 3042 (w), 3007 (w), 2928 (m), 2856 (w), 1626 (m), 1592 (m), 1482 (m), 1451 (m), 1413 (m), 1383 (w), 1325 (m), 1298 (w), 1238 (m), 1206 (m), 1177 (w), 1153 (m), 1104 (w), 1066 (w), 1020 (w), 1000 (w), 924 (w), 901 (w), 850 (w), 771 (w), 749 (s), 721 (s), 628 (w), 615 (w), 556 (w), 527 (w), 445 (w), 421 (m). Elemental analysis for C₂₁H₂₃N₃, calcd (%): C 79.46, H 7.30, N 13.24; found (%): C 79.61, H 7.41, N 13.41. Detailed characterization of HL and the intermediates are included in the ESI.†

Synthesis of 1a

A solvo thermal method⁴⁵ was used to synthesize the target complex 1a and 1b. The Cu_2O (4.32 mg, 0.03 mmol), HL (9.51 mg, 0.03 mmol), 1.5 mL of ethanol and 1.5 mL of water were added to a hard glass tube with an inner diameter of 8 mm, and the tube was sealed and heated to 140 °C for 72 h. After cooling the tube and its contents to rt at a rate of 3 °C per h, the contents were filtered and washed with ethanol to give a light yellow block crystal with a yield of about 52%. Elemental analysis for $C_{63}H_{66}N_9Cu_3$, calcd (%): C 66.15, H 6.06, N 10.74; found (%): C 66.38, H 5.84, N 11.06.

Synthesis of 1b

The Cu₂O (4.22 mg, 0.03 mmol), *HL* (9.51 mg, 0.03 mmol) and 3 mL of ethanol were added to a hard glass tube with an inner diameter of 8 mm, and the tube was sealed and heated to 140 °C for 72 h. After cooling the tube and its contents to rt at a rate of 3 °C per h, the contents were then filtered and washed with ethanol to give a colorless filamentous crystal with a yield of about 70%. Elemental analysis for $C_{63}H_{66}N_9Cu_3$, calcd (%): C 66.38, H 5.84, N 11.06; found (%): C 66.12, H 5.65, N 10.96.

Crystallographic studies

Single-crystal X-ray diffraction (SCXRD) data for **1a** and **1b** were collected by an Cryostream system (Oxford Cryosystems) on a XtaLAB PRO MM007 DW diffractometer system equipped with a RA-Micro7HF-MR-DW(Cu/Mo) X-ray generator and a Pilatus3R-200K-A detector (Rigaku, Japan), Cu $K\alpha$, $\lambda=1.54178$ Å. The numerical absorption corrections were applied using the ABSCOR program. The data set temperatures were 296 K and 100 K for **1a** and 298 K for **1b**. For **1a**, the structures were solved using direct methods, which yielded the positions of all the non-hydrogen atoms. These were first refined isotropically and

then anisotropically. All the hydrogen atoms of the ligands were placed in calculated positions with fixed isotropic thermal parameters and included in the structure factor calculations in the final stage of the full-matrix least-squares refinement.

For **1b**, the low quality of the crystal structure of the sample was due to poor data and a disorder problem of the flexible *n*-butyl chain and the carbazole ring, respectively. The cell parameters and atomic position of the CTC rings and heavy atom were generated from the SCXRD data by the Patterson method.

All the calculations were performed using the system of computer programs.^{46,47} The crystal data and structure refinement parameters are summarized in Table S1 (ESI†). Selected bond lengths and angles are given in Table S2 (ESI†).

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (no. 21731002, 21725304, 21975104, and 21901085), the Guangdong Major Project of Basic and Applied Research (2019B030302009), and the high-performance public computing service platform of Jinan University. G.-H. Ning thanks the Guangdong Basic and Applied Basic Research Foundation (2019B151502024), the Guangdong Province Pearl River Scholar Funded Scheme (2019), and the Fundamental Research Funds for the Central Universities (21619315) for their financial support.

Notes and references

- 1 A. J. McConnell, C. S. Wood, P. P. Neelakandan and J. R. Nitschke, *Chem. Rev.*, 2015, **115**, 7729–7793.
- 2 P. Theato, B. S. Sumerlin, R. K. O'Reilly and T. H. Epps III, *Chem. Soc. Rev.*, 2013, 42, 7055–7056.
- 3 Z. Fu, K. Wang and B. Zou, *Chin. Chem. Lett.*, 2019, **30**, 1883–1894.
- 4 L. Bai, P. Bose, Q. Gao, Y. Li, R. Ganguly and Y. Zhao, *J. Am. Chem. Soc.*, 2016, **139**, 436–441.
- 5 T. Ono, Y. Tsukiyama, A. Taema, H. Sato, H. Kiyooka, Y. Yamaguchi, A. Nagahashi, M. Nishiyama, Y. Akahama, Y. Ozawa, M. Abe and Y. Hisaeda, *ChemPhotoChem*, 2018, 2, 416–420.
- 6 H. Yan, F. Yang, D. Pan, Y. Lin, J. N. Hohman, D. Solis-Ibarra, F. H. Li, J. E. P. Dahl, R. M. K. Carlson, B. A. Tkachenko, A. A. Fokin, P. R. Schreiner, G. Galli, W. L. Mao, Z. X. Shen and N. A. Melosh, *Nature*, 2018, 554, 505–510.
- Y. Gu, H. Liu, R. Qiu, Z. Liu, C. Wang, T. Katsura, H. Zhang,
 M. Wu, M. Yao, H. Zheng, K. Li, Y. Wang, K. Wang, B. Yang,
 Y. Ma and B. Zou, *J. Phys. Chem. Lett.*, 2019, 10, 5557–5562.
- 8 Q. Li, Z. Chen, B. Yang, L. Tan, B. Xu, J. Han, Y. Zhao, J. Tang and Z. Quan, *J. Am. Chem. Soc.*, 2020, **142**, 1786–1791.
- 9 M. S. Kwon, J. Gierschner, J. Seo and S. Y. Park, *J. Mater. Chem. C*, 2014, **2**, 2552.

Edge Article Chemical Science

- 10 A. Pucci, Sensors, 2019, 19, 4969.
- 11 D. A. Davis, A. Hamilton, J. Yang, L. D. Cremar, D. Van Gough, S. L. Potisek, M. T. Ong, P. V. Braun, T. J. Martínez, S. R. White, J. S. Moore and N. R. Sottos, Nature, 2009, 459, 68-72.
- 12 J. W. Chung, Y. You, H. S. Huh, B.-K. An, S.-J. Yoon, S. H. Kim, S. W. Lee and S. Y. Park, J. Am. Chem. Soc., 2009, 131, 8163-8172.
- 13 Y. Wang, X. Tan, Y.-M. Zhang, S. Zhu, I. Zhang, B. Yu, K. Wang, B. Yang, M. Li, B. Zou and S. X.-A. Zhang, J. Am. Chem. Soc., 2015, 137, 931-939.
- 14 J. Kunzelman, M. Kinami, B. R. Crenshaw, J. D. Protasiewicz and C. Weder, Adv. Mater., 2008, 20, 119-122.
- 15 B. S. Li, X. D. Wen, R. P. Li, Z. W. Wang, P. G. Clem and H. Y. Fan, Nat. Commun., 2014, 5, 1-7.
- 16 W. Z. Yuan, Y. Tan, Y. Gong, P. Lu, J. W. Y. Lam, X. Y. Shen, C. Feng, H. H.-Y. Sung, Y. Lu, I. D. Williams, J. Z. Sun, Y. Zhang and B. Z. Tang, Adv. Mater., 2013, 25, 2837–2843.
- 17 S. Bergantin, M. Moret, G. Buth and F. P. A. Fabbiani, J. Phys. Chem. C, 2014, 118, 13476-13483.
- 18 Q. Qi, J. Qian, X. Tan, J. Zhang, L. Wang, B. Xu, B. Zou and W. Tian, Adv. Funct. Mater., 2015, 25, 4005-4010.
- 19 N. Li, Y. Gu, Y. Chen, L. Zhang, Q. Zeng, T. Geng, L. Wu, L. Jiang, G. Xiao, K. Wang and B. Zou, J. Phys. Chem. C, 2019, 123, 6763-6767.
- 20 H. Liu, Y. Gu, Y. Dai, K. Wang, S. Zhang, G. Chen, B. Zou and B. Yang, J. Am. Chem. Soc., 2020, 142, 1153-1158.
- 21 Y. Liu, Q. Zeng, B. Zou, Y. Liu, B. Xu and W. Tian, Angew. Chem., Int. Ed., 2018, 57, 15670-15674.
- 22 X. Sun, X. Wang, W. Liang, C. Gao, Z. Sui, M. Liu, R. Dai, Z. Wang, X. Zheng and Z. Zhang, J. Phys. Chem. C, 2018, 122, 15861-15867.
- 23 K. Nagura, S. Saito, H. Yusa, H. Yamawaki, H. Fujihisa, H. Sato, Y. Shimoikeda and S. Yamaguchi, J. Am. Chem. Soc., 2013, 135, 10322-10325.
- 24 B. Xu, Y. Mu, Z. Mao, Z. Xie, H. Wu, Y. Zhang, C. Jin, Z. Chi, S. Liu, J. Xu, Y.-C. Wu, P.-Y. Lu, A. Lien and M. R. Bryce, Chem. Sci., 2016, 7, 2201-2206.
- 25 Y. Gong, S. He, Y. Li, Z. Li, Q. Liao, Y. Gu, J. Wang, B. Zou, Q. Li and Z. Li, Adv. Opt. Mater., 2020, 8, 1902036.
- 26 L. Huang, C. Qian and Z. Ma, Chem.-Eur. J., 2020, 26, 11914-11930.
- 27 J. Yang, M. Fang and Z. Li, InfoMat, 2020, 2, 791-806.

- 28 J. Zheng, Z. Lu, K. Wu, G.-H. Ning and D. Li, Chem. Rev., 2020, 120, 9675-9742.
- 29 J. Zheng, H. Yang, M. Xie and D. Li, Chem. Commun., 2019, 55, 7134-7146.
- 30 Q. Li and Z. Li, Acc. Chem. Res., 2020, 53, 962-973.
- 31 C. H. Woodall, S. Fuertes, C. M. Beavers, L. E. Hatcher, A. Parlett, H. J. Shepherd, J. Christensen, S. J. Teat, M. Intissar, A. Rodrigue-Witchel, Y. Suffren, C. Reber, C. H. Hendon, D. Tiana, A. Walsh and P. R. Raithby, Chem.-Eur. J., 2014, 20, 16933-16942.
- 32 X.-C. Shan, F.-L. Jiang, D.-Q. Yuan, H.-B. Zhang, M.-Y. Wu, L. Chen, J. Wei, S.-Q. Zhang, J. Pan and M.-C. Hong, Chem. Sci., 2013, 4, 1484-1489.
- 33 S.-Z. Zhan, M. Li, X.-P. Zhou, J.-H. Wang, J.-R. Yang and D. Li, Chem. Commun., 2011, 47, 12441-12443.
- 34 J.-H. Wang, M. Li, J. Zheng, X.-C. Huang and D. Li, Chem. Commun., 2014, 50, 9115-9118.
- 35 W.-X. Ni, M. Li, J. Zheng, S.-Z. Zhan, Y.-M. Qiu, S. W. Ng and D. Li, Angew. Chem., Int. Ed., 2013, 52, 13472-13476.
- 36 R. Galassi, M. A. Rawashdeh-Omary, H. V. R. Dias and M. A. Omary, Comments Inorg. Chem., 2019, 39, 287-348.
- 37 O. Elbjeirami, M. D. Rashdan, V. Nesterov and M. A. Rawashdeh-Omary, Dalton Trans., 2010, 39, 9465.
- 38 S.-Z. Zhan, F. Ding, X.-W. Liu, G.-H. Zhang, J. Zheng and D. Li, Inorg. Chem., 2019, 58, 12516-12520.
- 39 L.-R. Xing, Z. Lu, M. Li, J. Zheng and D. Li, J. Phys. Chem. Lett., 2020, 11, 2067-2073.
- 40 Y. Gu, K. Wang, Y. Dai, G. Xiao, Y. Ma, Y. Qiao and B. Zou, J. Phys. Chem. Lett., 2017, 8, 4191-4196.
- 41 M. M. Olmstead, F. Jiang, S. Attar and A. L. Balch, J. Am. Chem. Soc., 2001, 123, 3260-3267.
- 42 H. V. Rasika Dias and C. S. Palehepitiya Gamage, Angew. Chem., Int. Ed., 2007, 46, 2192-2194.
- 43 P. F. McMillan, Chem. Commun., 2003, 8, 919-923.
- 44 L. D. Earl, J. K. Nagle and M. O. Wolf, Inorg. Chem., 2014, 53, 7106-7117.
- 45 R.-J. Wei, H.-G. Zhou, Z.-Y. Zhang, G.-H. Ning and D. Li, CCS Chem., 2020, 2, 2045-2053.
- 46 C. B. Hübschle, G. M. Sheldrick and B. Dittrich, J. Appl. Crystallogr., 2011, 44, 1281-1284.
- 47 G. M. Sheldrick, Acta Crystallogr., Sect. A: Found. Crystallogr., 2008, 64, 112-122.