

# Recent progress in the preparation of polyaniline nanostructures and their applications in anticorrosive coatings

Cite this: *RSC Adv.*, 2014, 4, 28195

Zhifei Tian, Haojie Yu,\* Li Wang,\* Muhammad Saleem, Fujie Ren, Pengfei Ren, Yongsheng Chen, Ruoli Sun, Yubiao Sun and Liang Huang

Received 8th April 2014  
Accepted 29th May 2014

DOI: 10.1039/c4ra03146f

[www.rsc.org/advances](http://www.rsc.org/advances)

Research on composites/blends containing polyaniline (PANI) has attracted numerous scientists and engineers due to their excellent adhesion and anticorrosive properties. Nano-structured PANI composites and matrix resins play a key role in physical and anticorrosive performance. This paper reviews the synthesis, growth mechanisms and corrosion application with different resin coatings of PANI-based nano-composites. It also highlights the failures of corrosion protection and methods and suggestions to improve it.

## 1. Introduction

Corrosion can lead to enormous economic costs and damage to modern industrial societies, which have a bad impact on humans and the surrounding environment. It has been reported that corrosion consumes more than 3% of the gross domestic product (GDP) of the world annually.<sup>1–3</sup>

One of the most commonly practiced techniques to prevent metals from corrosion is to apply anticorrosive paints on their surfaces. Commonly used anticorrosive paints, such as epoxy, polyurethane, polyester, *etc.*, are formulated from thermosetting resins, which are not long-lasting. Once a scratch or hole forms in the coating, the corrosive easily attacks the matrices. To improve their anticorrosion performance, anticorrosive coatings must contain corrosion inhibitors such as lead compounds and chromate pigments.<sup>4</sup> However, due to the adverse effects of heavily used chromium and lead, the environment protection authority and other environmental organizations mandate the elimination of their use as pigments for anticorrosion paint. Sacrificial coatings that use zinc particles as pigments have been designed for heavy duty protection to minimize pollution. However, this type of coating is quite easily corroded due to its poor physico-chemical properties, which significantly limits its use in the shipping industry.<sup>5</sup>

Conducting polymers gained much attention during the past two decades because of their environmentally friendly behavior as well as their unusual corrosion inhibiting action for

metals.<sup>6–12</sup> Among these conducting polymers, polyaniline is considered to be one of the best anticorrosive materials<sup>13–15</sup> not only because of its unique redox tunability, environmental stability and simple acid–base doping–dedoping process,<sup>16</sup> but also because passivation of oxide layer between metal and coating is induced by PANI, which protects the metal from further corrosive attack.<sup>17</sup> PANI nanoparticles are of great interest to researchers because of their unique quantum size effect, small size effect and surface effect. They have demonstrated enhanced performance in applications such as corrosion protection,<sup>18–22</sup> electrochromic devices,<sup>23</sup> sensors,<sup>24</sup> biomimetic scaffolds,<sup>25</sup> energy storage<sup>26–28</sup> and supercapacitors.<sup>29–31</sup> Therefore, it is of both great technological and scientific interest to investigate anticorrosive composites/blends containing PANI nanostructure. Although several articles on PANI<sup>32–35</sup> have been devoted to the preparation of PANI nanofibers and nanotubes, in this review we narrow down our discussion on the recent preparation of various PANI nanostructures and their applications on improving adhesion and hydrophobicity, as well as the anticorrosion of coatings.

## 2. Preparation of PANI nanostructures

There are various methods for preparing nanoscale PANI such as heterophase interfacial, solution, self-assembling and electrochemical polymerizations.<sup>36–39</sup> Fig. 1 shows a schematic summary of the oxidation of aniline, which also presents some significant factors affecting the morphology alone or synergism during the synthesis process. In addition to the core parameters (yellow color) for oxidizing aniline, to tailor the type of desired nanostructure, other reaction parameters and processes (blue color) should be taken into consideration.<sup>40,41</sup> These parameters

State Key Laboratory of Chemical Engineering, Department of Chemical and Biological Engineering, Zhejiang University, Hangzhou 310027, China. E-mail: [hjyu@zju.edu.cn](mailto:hjyu@zju.edu.cn); [opl\\_wl@zju.edu.cn](mailto:opl_wl@zju.edu.cn); [tian.zhifei@live.cn](mailto:tian.zhifei@live.cn); [chemist.saleem786@gmail.com](mailto:chemist.saleem786@gmail.com); [lamrenfujie@126.com](mailto:lamrenfujie@126.com); [1989guoyunyu@163.com](mailto:1989guoyunyu@163.com); [josephchan0314@gmail.com](mailto:josephchan0314@gmail.com); [sun\\_ruoli@163.com](mailto:sun_ruoli@163.com); [sunyu.biao@163.com](mailto:sunyu.biao@163.com); [a314630828@163.com](mailto:a314630828@163.com); Fax: +86-571-8795-1612; Tel: +86-571-8795-3200

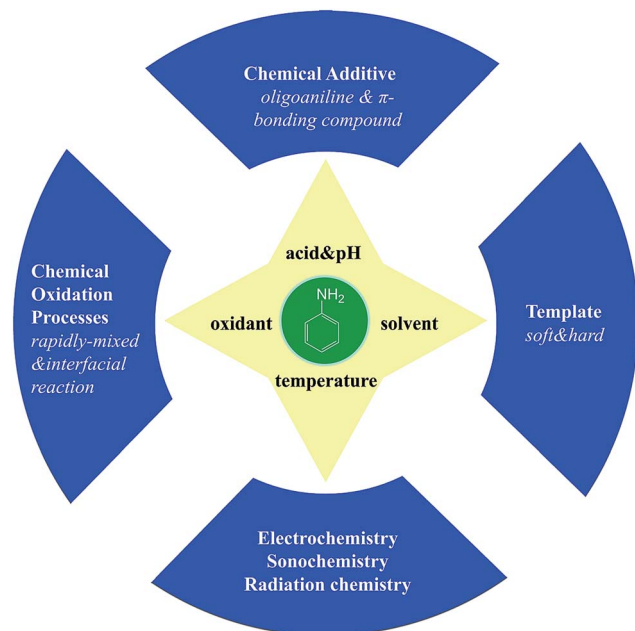


Fig. 1 Schematic summary of synthetic pathways for the oxidation of aniline.

and processes include chemical additives introduced to the oxidation, type of template used, polymerization and equipment employed.<sup>42</sup> Although the processes for producing PANI nanostructures are quite complicated, they can be divided into two routes: those that rely on external templates to induce the growth of nanostructure and those that do not.<sup>43</sup> Corrosion chemists are trying to synthesize well-designed PANI composites to realize superhydrophobic surface and various nanostructures.<sup>44</sup> Template synthesis is an efficient method for producing superior anticorrosion nanoscale PANI composites. As the most straightforward method for synthesizing PANI nanostructures, the template route includes soft-template and hard-template methods. The former, also named as the self-assembly method,<sup>45</sup> relies on micelles formed by surfactants to confine the polymerization of PANI into one-dimensional nanostructures. Compared to the soft-template synthesis, the monomer or its salt forms micelles by itself in the non-template synthesis. The hard-template employs some particles as a scaffold such that PANI can grow on the surface of particles to acquire a certain morphology.

Scheme 1 shows certain initial oligoanilines to synthesize PANI.<sup>46</sup> Reaction through the *ortho* position can lead to further oxidation, which produces phenazine-like moieties along the backbone of the polymer. Aniline reacting through tail-to-tail coupling will produce benzidine moieties, and through head-to-head coupling it will produce azobenzene. Furthermore, *ortho*-coupled units may undergo intramolecular cyclization to produce phenazine structures, which play the role of nucleates in chain propagation.<sup>47</sup> The relatively flat molecular structure of the phenazine moiety makes them hydrophobic and allows them to maintain one-dimensional nanostructures stable by  $\pi$ - $\pi$  interactions. They can deposit on various surfaces to

become orderly arranged in the nanostructure with outward benzene rings.<sup>48</sup> Since they form a basis for the proposed self-assembly processes, these possible reactions of aniline during its initial stages of oxidation are crucial for understanding several mechanisms of nanostructure formation.<sup>49–51</sup> The hydrophobic property and the various nanostructures are crucial for corrosion protection,<sup>52</sup> making the formation of phenazine-containing structure an important part of the synthesis of PANI composites. Then, a series of organizations of nucleates, including disordered self-assembly, stacking, adsorption at polymer chains, or adsorption on immersed surfaces occurs exclusively, successively or simultaneously, depending on the experimental conditions.<sup>42,53</sup>

The reversible acid–base, doping–dedoping, oxidation–reduction chemistry of polyaniline is shown in Scheme 2.<sup>54</sup> Leucoemeraldine, known as the fully reduced form of polyaniline, can be fully oxidized to form pernigraniline or half-oxidized to form emeraldine. The emeraldine base (EB) form of polyaniline is electrically insulating, and can be doped with a strong acid to give the electrically conducting emeraldine salt (ES) form of PANI. By adding a strong base, ES can be reversed to electrically insulating EB. This reversible conductivity achieved by doping can be applied in actuators and batteries;<sup>32</sup> the unique redox tenability plays a constructive role in keeping the metal in the passivation state.<sup>55</sup>

Nucleates and aniline are sensitive to slight changes during the reaction condition, which leads to PANI's propensity for forming numerous different structures. Schematic diagrams of processes for the preparation of different morphologies of PANI composites are shown in Fig. 2. In particular, the diversity of PANI nanostructures offers the possibility of enhanced performance wherever a high interfacial area is required between the atmosphere and PANI.<sup>56</sup> For example, PANI nanostructures display much higher anticorrosion properties and better impact toughness relative to their conventional bulk counterparts in anticorrosive coatings due to higher effective surface areas and better contact with metals or resins.<sup>57</sup> Different PANI-based composites with various morphologies applied in specific circumstances are shown in Table 1.

## 2.1. PANI-based granules

By using strong oxidants and high aniline concentrations under strongly acidic conditions, *e.g.*, ammonium persulfate (APS) or potassium permanganate in sulfuric acid, a granular morphology of PANI powders is most commonly observed by precipitation polymerization.<sup>58</sup> As shown in Fig. 2, it is assumed that nano-granules are achieved by a random process of nucleates getting together. Such a situation may occur due to an extremely high concentration of nucleates, which are produced during the short induction period. When the growth of PANI chain begins to burst, nucleates start aggregating. Nucleates in water have a limited solubility, and therefore they randomly agglomerate in continuous phase to give a bigger granule by stacking. Mechanical agitation is known to affect the nucleation of some materials, including PANI. Under the shear force condition, heterogeneous nucleation occurs on the surfaces of

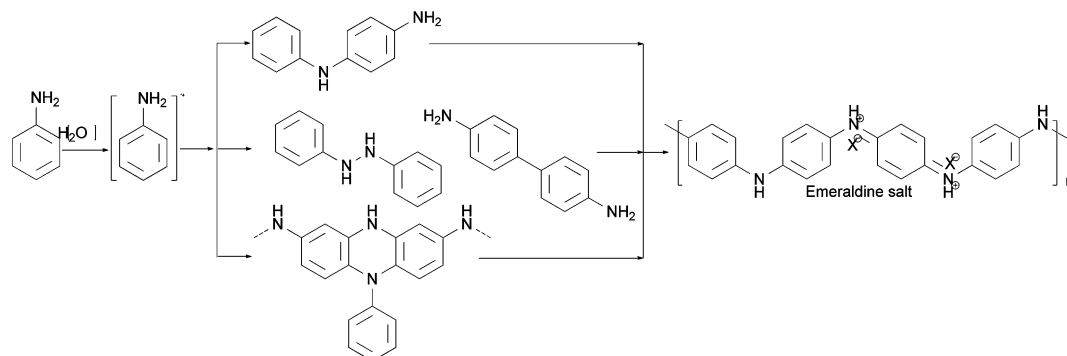
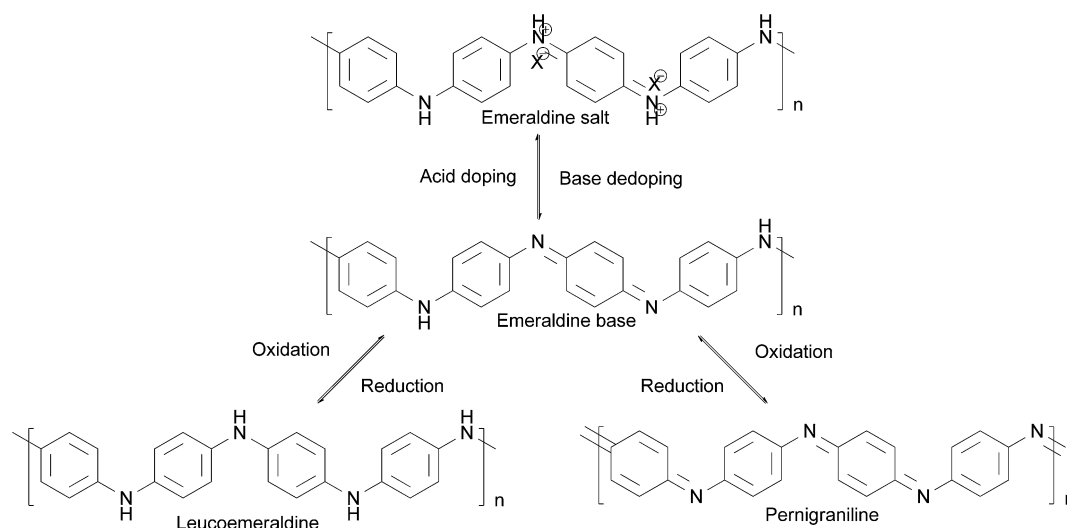
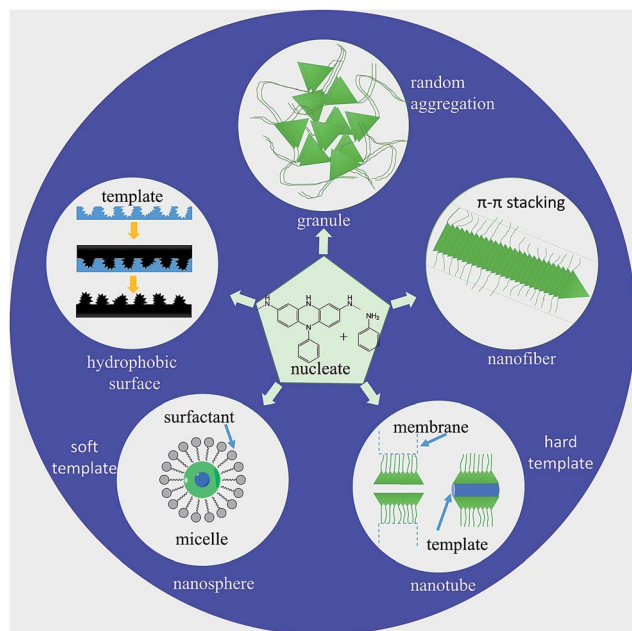
Scheme 1 Different initial stages of oxidation to obtain PANI.<sup>46</sup>Scheme 2 Oxidation–reduction reaction of PANI.<sup>54</sup>

Fig. 2 Schematic illustration of nucleates and monomer of aniline to produce different types of PANI nanostructures.

the preformed particles. Thus, hydrophobic nucleates adsorb on the formed PANI granules as nanoscale glues to link the particles together, and also initiate the growth of new granules on the surface of the former. Finally, fused granular morphology is generated. Fig. 3 shows the granular morphology of PANI, which was synthesized by stirring aniline with APS in phosphoric acid for 6 hours at 30 °C. Most anticorrosion coatings use granular PANI powders as corrosion inhibitors;<sup>59</sup> to attain higher corrosion resistance other morphologies of PANI can be added.<sup>60</sup>

## 2.2. PANI-based nanofibers

PANI nanofiber composites are one-dimensional objects with a typical diameter of tens of nanometers. There are five basic efficient methods for the preparation of nanofibers:<sup>43</sup> (I) rapidly mixed reaction,<sup>61</sup> (II) interfacial polymerization,<sup>62</sup> (III) dilution technique,<sup>63</sup> (IV) seeding method<sup>64</sup> and (V) electrospun technique.<sup>65</sup> The formation mechanisms of polyaniline nanofibers are quite similar and were fully studied by Huang *et al.*<sup>66</sup> They concluded that the key to synthesizing PANI nanofiber was preventing the secondary growth of the nucleate. It is assumed

Table 1 Different PANI-based composites in the class of morphologies

Different morphology of PANI-based	Composition of corrosion inhibitor <sup>a</sup> [Ref.]	Doped acid <sup>b</sup>	Methods of composite preparation	Metal used	Corrosive medium
Granules	ND-PANI <sup>6</sup> PANI-CN <sup>85</sup>	HCl —	<i>In situ</i> polymerization Ultrasonic oxidative polymerization	Steel and aluminum Carbon steel	HCl 3.5% NaCl
Nanofibers	ZnO-PANI <sup>22</sup> PANI <sup>20</sup> PANI <sup>69</sup>  PANI <sup>98</sup>	CSA Lignosulfonate H <sub>2</sub> SO <sub>4</sub>  H <sub>3</sub> PO <sub>4</sub> -HCl- H <sub>2</sub> SO <sub>4</sub> -HNO <sub>3</sub>	<i>In situ</i> polymerization Direct mixed reaction Three different type of reactions Direct mixed reaction	Carbon steel Aluminum alloy Mild steel Steel type Q 235	3.5% NaCl 0.6 M NaCl 3.5% NaCl 3.5% NaCl
Nanotubes	PANI-MWCNT <sup>74,91</sup> PANI <sup>73</sup>	HCl-DBSA DBSA	<i>In situ</i> polymerization Emulsion polymerization	Mild steel Mild steel	3.5% NaCl 3.5% NaCl
Nanospheres	PANI shell with AuNPs <sup>75</sup>  SiO <sub>2</sub> with PANI core-shell spheres <sup>76</sup> PANI/P-PVA <sup>104</sup>	3-Nitrosali-cylic acid DBSA  H <sub>3</sub> PO <sub>4</sub> -HCl	<i>In situ</i> polymerization and dispersion mixing Conventional polymerization	Zinc Cold-rolled steel	1 M KCl 3.5% NaCl
Other nano-composites	HEE and SEPI synthesized from ACAT <sup>121,122</sup> Urchin-like PANI <sup>81,82</sup>	— β-cyclodextrins-HCl	Conventional polymerization Nanocasting technique Emulsion polymerization and <i>in situ</i> polymerization	Steel Cold-rolled steel —	3.5% NaCl 3.5% NaCl —

<sup>a</sup> ND-PANI, nano-diamond-polyaniline; PANI-CN, polyaniline clay nano-composite; PANI-MWCNT, multi-wall carbon nanotube-polyaniline; PANI/P-PVA, polyaniline/partially phosphorylated poly(vinyl alcohol); HEE, hydrophobic electroactive epoxy; SEPI, superhydrophobic electroactive polyimide; ACAT, amine-capped aniline trimer. <sup>b</sup> CSA, camphor sulfonic acid; DBSA, dodecylbenzene sulfonic acid.

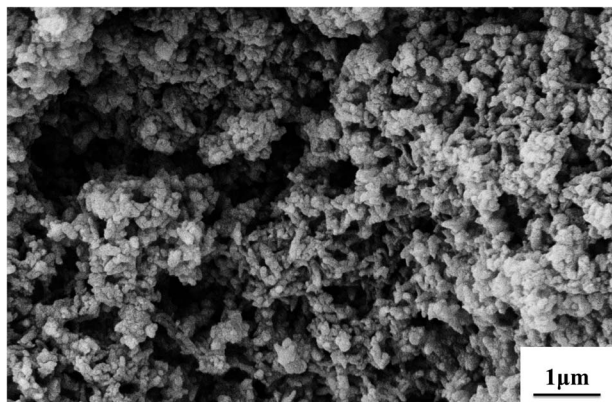


Fig. 3 SEM images of granular PANI powder morphology. Synthetic conditions: [aniline] = 0.5 M, [aniline]-[APS] = 2 : 1, [H<sub>3</sub>PO<sub>4</sub>] = 1 M.

that under suitable conditions, aniline nucleates are prone to stacking and are stabilized by  $\pi$ - $\pi$  interactions between phenazine-containing structures, which is shown in Fig. 2. The nucleates induce the formation of nanofibers in their vicinity, and then act as the main part of a nanofiber for continuing growth. In contrast to the formation of granule morphology, homogeneous nucleation of PANI leads to nanofibers, whereas heterogeneous nucleation results in granular particulates. During rapidly mixed reactions, quick consumption of the reactants limits secondary growth, resulting in the nanofiber morphology.<sup>40</sup> In interfacial polymerization, PANI nanofibers form at the interface, where aniline reacts with the oxidant. This process also carries the nanofibers away from the reaction

interface, which suppresses the secondary growth of irregular particles. New nucleates can stack on different directions of the growing nanofibers, thus extending the one-dimensional structure to a network columnar structure. The adsorption of free nucleates at the nanofibers results in their branching.<sup>67</sup> Li *et al.*<sup>68</sup> reported a facile rapid polymerization route to synthesize high quality PANI nanofibers initiated by APS/Fe<sup>2+</sup> redox initiator. Different concentrations of HCl play a crucial role in the formation of PANI nanofiber morphology. In addition, the composition of redox initiator and the molar ratio of aniline to redox initiator influences the size and morphology of the polyaniline nanofibers. As shown in Fig. 4, only with concentrations of HCl in a certain range could the author produce PANI nanofibers.<sup>68</sup> As the concentration of HCl increased, diameters of polyaniline nanofibers became longer. These nanofibers had a high aspect ratio, whose formation process was free of any templates or surfactants. Because better impact toughness and higher anticorrosion property can be achieved due to higher effective surface areas and shorter penetration depths of target molecules,<sup>69</sup> PANI nanofiber composites are widely applied in corrosion protection.<sup>70,71</sup>

### 2.3. PANI-based nanotubes

Nanotubes, which have an internal cavity in the middle, are one-dimensional objects such as nanofibers. PANI nanotubes are one of the most interesting objects among nanostructures in the conducting polymer family. PANI nanotubes can be prepared by physical approaches and chemical routes such as soft-template synthesis, hard physical template-guided synthesis and electrospinning synthesis. The formation





Fig. 4 SEM images of polyaniline nanofibers synthesized using different concentrations of HCl. (a) 0.01 M; (b) 0.2 M; (c) 0.5 M; (d) 1 M. Synthetic conditions: [aniline] = 0.05 M, [aniline]–[APS] = 4 : 1, [APS]–[Fe<sup>2+</sup>] = 3 : 2, and 6 h.<sup>68</sup>

mechanism of nanotubes around a template is similar to that of nanofibers.<sup>34</sup> PANI-based nanotubes are produced growing nucleates under the guidance of templates such as inside membrane pores and on the surface of template structures. Pan *et al.*<sup>72</sup> developed a reactive template method for producing the PANI nanotube. MnO<sub>2</sub> was assumed to be the template and oxidant. When the oxidation of aniline occurred on the surface of the manganese oxide template, MnO<sub>2</sub> was consumed, leading to a hollow PANI structure (Fig. 5). Various morphologies should be possible by simply changing the shape of MnO<sub>2</sub>. Mahmoudian *et al.*<sup>73</sup> exhibited the effect of PANI nanotubes and

nanofibers in polyvinyl butyral coating on corrosion protective performance of mild steel. It was confirmed that the resistance of the coating containing PANI nanofibers was three times lower than that containing PANI nanotubes after 30 days of immersion. This effect was explained by the lower surface area of the nanofibers compared to nanotubes of the same mass. To produce PANI nanotubes, Deshpande *et al.*<sup>74</sup> used multi-wall carbon nanotubes (MWCNT) as a template and synthesized PANI over this template. It was observed that the corrosion rate of low-carbon steel coated with the composite as an anticorrosive was about 3.6 times lower than that of epoxy painted steel.

## 2.4. PANI-based nanospheres

PANI nanospheres with a diameter of around 200 nm, whether hollow or not, are expected to be promising candidates in academic applications of anticorrosion.<sup>75,76</sup> Soft-template is a typical method to synthesize PANI-based nanospheres. As shown in Fig. 2, micro-emulsion polymerization can be applied to produce nanocapsules and nano-composites. Surfactants are usually used for the formation of micelles; the oxidation of aniline and self-assembly of nucleates occurs inside the micelles to achieve the final nanosphere morphology. In acetone solution, uniform PANI nanospheres were successfully synthesized by using cellulose acetate (CA) as a single template, which provided the first example of uniform PANI nanospheres synthesized in a non-aqueous system.<sup>77</sup> Fig. 6 shows the morphology of PANI nanospheres prepared by the oxidation of aniline in phosphoric acid aqueous solution using APS as an oxidant; aniline forms micelles by itself. PANI nanosphere composite has high specific surface when mixed with a resin, and shows better solvation and excellent hydrophobic interaction on the surface. Lv *et al.*<sup>78</sup> successfully synthesized PANI

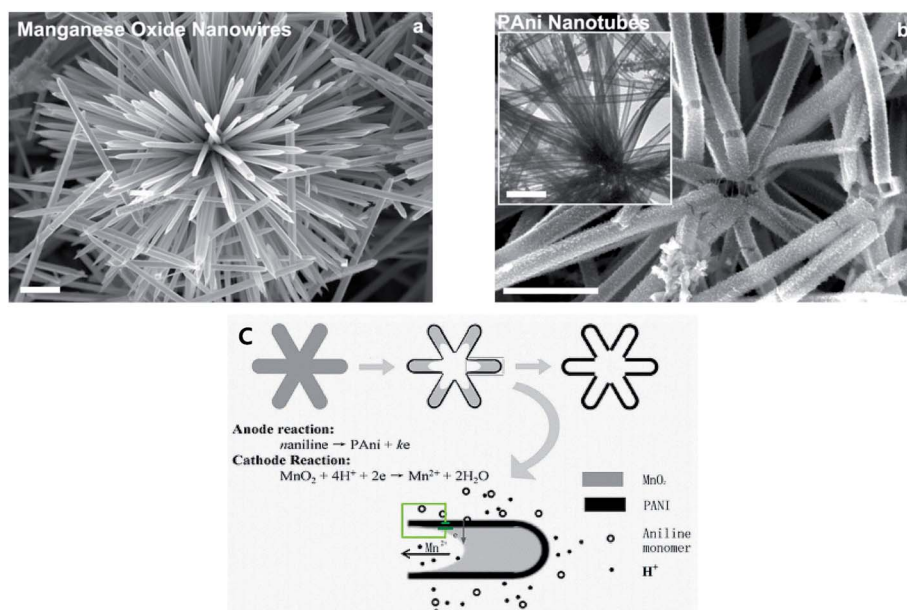


Fig. 5 SEM images of (a) cryptomelane-phase manganese oxide template. (b) Resultant polyaniline nanotubes. Inset of (b) is a TEM image of polyaniline nanotubes. (c) Schematic illustration of possible microzone galvanic cell reaction occurring during the conversion from manganese oxide wire to PANI nanotube. The scale bar is 1  $\mu$ m.<sup>72</sup>

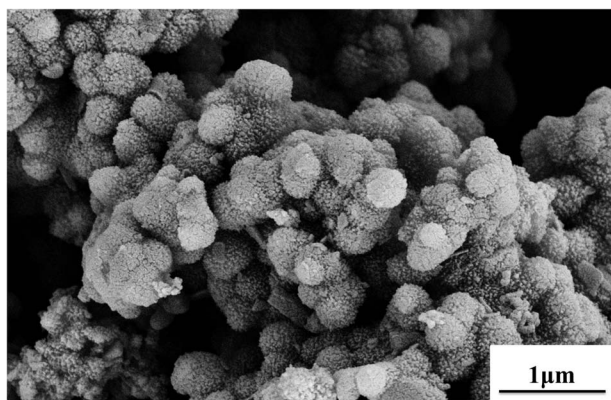


Fig. 6 SEM images of PANI nanosphere prepared in phosphoric acid. Synthetic conditions: [aniline] = 0.2 M, [aniline]–[APS] = 4 : 5, [H<sub>3</sub>PO<sub>4</sub>] = 1 M.

nanocapsules by using the interface of mini-emulsion droplets as a template. A hydrophobic liquid self-healing agent, whose release could be stimulated upon reduction and delayed under oxidation, was encapsulated in the PANI capsules, making them promising candidates for self-healing applications and anti-corrosion in metallic systems.

### 2.5. Other morphologies

Zhu *et al.*<sup>79</sup> synthesized conductive rambutan-like hollow spheres of PANI, which were self-assembled by using per-fluorooctane sulfonic acid (PFOSA) as a dopant and a soft template, causing super-hydrophobicity simultaneously. The morphological evolution of PANI helixes<sup>80</sup> was achieved by a facile process through the generation of onion-like, multi-lamellar vesicles used as a novel soft template and a liquid crystal acting as a promoter for PANI polymerization and self-assembly, which is a breakthrough in the synthesis of helical structures. Whether solid or hollow, the urchin-like PANI nanoparticles with an average radius of 60–200 nm have been successfully prepared by Prasannan *et al.*<sup>81</sup> and Yang *et al.*,<sup>82</sup> as shown in Fig. 7(a) and (b), respectively. The solid urchin-like PANI nanoparticles were synthesized selectively using  $\beta$ -CD-mediated micro emulsion polymerization in the presence of FeCl<sub>3</sub> as a structure-directing agent, while the hollow nanoparticles were successfully synthesized by applying polystyrene spheres as template and support. FeCl<sub>3</sub> was also used as a mild oxidant and structure-directing agent. Zhao *et al.*<sup>48</sup> studied the interactions between the aniline oligomer and the molecules of the medium and synthesized three-dimensional assemblies of flower-like and urchin-like microspheres, whose contact angle of the surface was surprisingly high at 153.7°. Peng *et al.*<sup>83</sup> prepared a PANI film with biomimetic superhydrophobic structures using a nanocasting technique. The illustration of *Xanthosoma sagittifolium* replication is shown in Fig. 2. Polydimethylsiloxane (PDMS) was used as a template to replicate the superhydrophobic surface of leaves to PANI, which produced good morphology and corrosion protected PANI film. All the PANI-based nanostructures mentioned above have high contact

angle and exhibit super-hydrophobicity, which always contribute to prominent anticorrosion property.

## 3. PANI nanostructure-based anticorrosive coatings

Although pure PANI shows good anticorrosion property,<sup>84–86</sup> the benefits of the application of PANI are hindered by its poor solubility, infusibility, as well as its almost non-processable properties.<sup>87,88</sup> There are two basic methods for producing PANI-containing composites and improving the applications of PANI: (I) mixing PANI composites with matrix polymer by mechanical dispersion;<sup>89–91</sup> (II) synthesizing PANI composites in the presence of matrix to improve dispersibility.<sup>92</sup> The significance of these processes is their convenient processibility and low price. The advantages and disadvantages of coating systems containing PANI composites and their preparation methods are given in Table 2.

Since pure PANI is neither soluble nor fusible in water as well as in organic solvents, the soluble and heat-processable polymer materials containing PANI have gradually become one of the important topics in materials science.<sup>93,94</sup> In common solvents, the development of better solubility of PANI was first achieved by Cao *et al.*<sup>95</sup> They reported that the counter-ion could induce the processibility of the resulting polyaniline complex by using a suitably functionalized protonated polyaniline. The use of oxide passive film, which is formed by the interaction of polyaniline and steel, implied that pure PANI coating film on the surface of mild steel had a good protective effect but its corrosion protection was short term due to its poor barrier to water.<sup>96</sup> To achieve long-term protection of metal, it is necessary to develop a blended coating containing both conventional resin and PANI.

### 3.1. Polyaniline epoxy resin coatings for corrosion inhibition

Epoxy resin is widely applied in the coating industry because of its superb adhesion to metals and high resistance to heat and corrosive solvent.<sup>97</sup>

Ge *et al.*<sup>98</sup> prepared PANI nanofibers using four kinds of different dopant acids by rapidly mixed reaction. The best morphology with uniform diameter and several microns length was observed, especially in H<sub>2</sub>SO<sub>4</sub>. The study also found that the curing time of epoxy resin could be delayed by adding PANI. Morphology and counter-anion would impact the anticorrosion effect of the doped PANI. It was observed that H<sub>3</sub>PO<sub>4</sub>-doped PANI showed the best protective effect, followed by H<sub>2</sub>SO<sub>4</sub>-doped PANI, and then by HNO<sub>3</sub>-doped PANI and HCl-doped PANI. In addition to increased corrosion resistance, epoxy–PANI composites improved other unique properties such as thermal, mechanical and conductivity properties.<sup>99,100</sup> For example, PANI can act as a curing agent for epoxy resin with covalent bonds formed between the amine groups of PANI and the epoxy groups of epoxy resin; the heat to cure increases as PANI loading increases.<sup>101</sup> Electrical conductivity of the epoxy–PANI nanocomposites has been achieved by increasing the loading<sup>102</sup> or decreasing the size<sup>98</sup> of PANI, and the morphology effect was

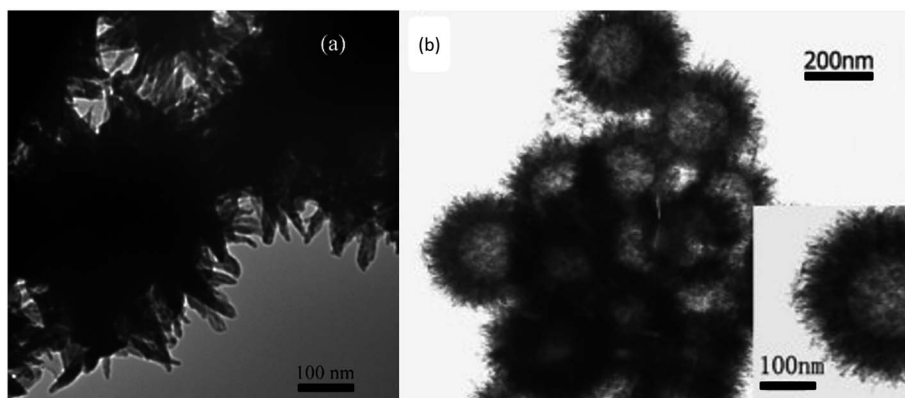


Fig. 7 TEM images of urchin-like (a) PANI nanorods prepared through the chemical polymerization of corresponding monomer complex ( $\beta$ -CD and aniline are in equal moles).<sup>81</sup> (b) PANI hollow spheres obtained by dispersing hollow spheres preloaded with anilinium salt solution into ferric chloride solution.<sup>82</sup>

Table 2 Different PANI-based composites in the class of organic coating system

Organic coating system	Composition of corrosion inhibitor <sup>a</sup> [Ref.]	Methods of coating preparation	Advantage	Disadvantage
PANI film	ND-PANI <sup>6</sup> CNTs-PANI <sup>19,69</sup>	Chemical/electrochemical polymerization	Great anticorrosion property	Poor solubility, infusible, non-processable properties
Epoxy resin	PANI-lignosulfonate; <sup>20</sup> ZnO-PANI; <sup>22</sup> PANI-MWCNT; <sup>74,91</sup> nano-PANI; <sup>88,98</sup> PANI/P-PVA <sup>104</sup>	Solution blending matrix polymers and PANI	High resistance to heat, water or chemicals; excellent adhesion to metals; PANI acts as curing agent for epoxy resin	Ease to chalking and yellowing when exposed to ultraviolet radiation
Polyurethane	PANI and PNA; <sup>105,106</sup> DBSA doped PANI <sup>108,110</sup>	Solution blending matrix polymers and PANI; copolymerization of oligoaniline with other monomers	Low color change, high gloss retention and scratch resistance	Poor resistance towards mechanical strains, deformation or degradation at high temperatures
Polyimides	SEPI <sup>123</sup>	Copolymerization of oligoaniline with other monomers	Striking dielectric, thermal, adhesive, dimensional stability	Poor resistance to alkalis or inorganic acids
Alkyd resin	PANI doped with HCl-DBSA-CSA-TSA; <sup>87</sup> PANI and PNA; <sup>96</sup> PANI-EB/ES <sup>117</sup>	Solution blending matrix polymers and PANI	Good adhesion, flexibility, resistance to acid, and durability	Poor resistance to caustic alkali
Polyvinyl butyral (PVB)	PANI nanotubes; <sup>73</sup> PANI shell with AuNPs <sup>75</sup>	Solution blending matrix polymers and PANI	Strong binding, optical clarity, adhesion to many surfaces, toughness and flexibility	Poor resistance to chemical and high temperature
Acrylic polymers and copolymers	PANI (PPA) and PANI (CSA) <sup>113</sup>	Solution blending matrix polymers and doped PANI counter-ion-induced processibility	Good adhesion, chemical inertness, photo stability, and environmental stability	Limited resistance in water or soil
Chlorinated rubber	PANI-ES/EB and DBSA-doped PANI <sup>119</sup>	Solution blending matrix polymers and PANI	Excellent resistance to water	Poor solvent resistance and high VOC content

<sup>a</sup> ND-PANI, nano-diamond-polyaniline; PANI-MWCNT, multi-wall carbon nanotube-polyaniline; PANI/P-PVA, polyaniline/partially phosphorylated poly (vinyl alcohol); PNA, poly(1-naphthylamine); SEPI, superhydrophobic electroactive polyimide; CSA, camphor sulfonic acid; DBSA, dodecylbenzene sulfonic acid; TSA, *p*-toluene sulfonic acid; PANI(PPA), phenylphosphonate-doped polyaniline; PANI (CSA), camphor sulfonic acid-doped polyaniline; ES, emeraldine salt; EB, emeraldine base.

studied by Zhang *et al.*<sup>103</sup> For the conductivity study, at the same loading level, volume resistivity in epoxy nano-composites with PANI nanofibers was lower than that in epoxy nano-composites

with PANI nanospheres. The junctions of PANI nanospheres with lower aspect ratio were more than those in the PANI nanofibers with higher aspect ratio. Compared to pure epoxy,



the improved dielectric property was attributed to the large interfacial polarization of polymer nano-composites. Chen and Liu<sup>104</sup> successfully synthesized conducting polyaniline/partially phosphorylated poly (vinyl alcohol) (PANI/P-PVA) spherical nanoparticles with better dispersion. Variations in the open circuit potential (OCP) values and electrochemical impedance spectroscopy (EIS) spectra with time of exposure demonstrated that waterborne PANI/P-PVA-containing coatings with PANI/P-PVA content of 2.5 wt% were able to offer higher corrosion protection than PANI ES-containing coatings with PANI ES content of 2.5 wt% because of significant dispersibility in aqueous and uniform distribution of the former system. The appearance of three-coated panels after salt spray test for 30 days is shown in Fig. 8, which confirmed that severely bubbled or obvious corrosion was not observed on the 2.5 wt% PANI/P-PVA coating.

### 3.2. Polyaniline polyurethane coatings for corrosion inhibition

The advantage of polyurethane coatings is their remarkable resistance to ultraviolet radiation and weather. Compared to epoxy coatings, they are also widely used for corrosion protection,<sup>105,106</sup> especially in an environment where sunlight is abundant, because this type of coating exhibits low loss of gloss and color change when exposed to ultraviolet radiation.<sup>107</sup> Due to good abrasion resistance, hardness, gloss, general chemical resistance, and impact resistance coupled with zero or low volatile organic compound (VOC) emissions, waterborne polyurethane dispersions are widely investigated. Gurunathan *et al.*<sup>108</sup> for the first time used aqueous cationomeric polyurethane dispersions (PUDs) blending with 2 wt%, 4 wt% and 6 wt% of polyaniline–dodecyl benzene sulfonic acid (DBSA) water dispersions to form new conductive composites. Accelerated corrosion tests revealed that PUD-2000–PANI 6% showed superior corrosion protection on mild steel coupons, which can be observed in Fig. 9. The numbers in the names are different polyols used in the experiment. Moreover, as reported by Chen *et al.*,<sup>109</sup> fibrous structure of DBSA-doped PANI was prepared

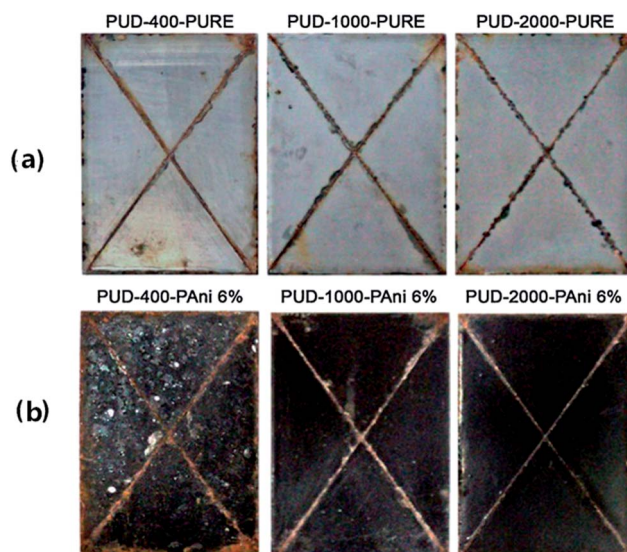


Fig. 9 Photographs showing MS panels coated with (a) pure and (b) blended polymers after exposing to salt spray test (300 h).<sup>108</sup>

and well-dispersed in the conducting waterborne polyurethane (WPU) matrix. These blends of conducting films can be used for corrosion protection, for antistatic requirements and in other fields. Different results were found by Diniz *et al.*,<sup>110</sup> who compared organic coatings based on epoxy and polyurethane matrices containing PANI doped with DBSA. PANI had an adverse effect on polyurethane paints by a decrease in resistance, whereas the epoxy-based coatings exhibited improved performance due to different interactions of PANI–DBSA pigments with different matrices.

### 3.3. Polyaniline acrylic polymer coatings for corrosion inhibition

Acrylic polymers and copolymers are widely used in the formulation of protective coatings due to their good adhesion, film-forming properties and photo-stability. Sathiyarayanan *et al.*<sup>111,112</sup> investigated the comparative anticorrosive



Fig. 8 Photograph of pure epoxy-coated panel, 2.5 wt% PANI ES-coated panel, and 2.5 wt% PANI/P-PVA-coated panel after 30 days of exposure to salt spray test.<sup>104</sup>



performance of coatings containing  $\text{TiO}_2$ , PANI and PANI- $\text{TiO}_2$  composites (PTC) on steel in an acrylic binder. The performance of the coatings containing a granule morphology of the above mentioned three samples was evaluated by immersion test in 3% NaCl for 60 days, salt fog test for 35 days and OPC and EIS technique. Results showed that the OPC values of PTC-containing coating were higher than that of the coatings with  $\text{TiO}_2$  or PANI. PTC coating resistance values were two orders higher than the others. The author considered that the enhanced performance of PTC coatings was due to a uniform distribution of granule PANI instead of bulk PANI, which could form a more uniform passive film to protect the surface. Silva *et al.*<sup>113</sup> investigated the electrochemical behaviors of polymeric blends formed by phenylphosphonate (PPA)-doped PANI and camphorsulphonate (CSA)-doped PANI, both of which were used as corrosion inhibitors for iron in sulphuric acid solutions with or without chloride ions. This study showed that the chemical nature of the dopant acid used for preparing PANI was a crucial choice, which would determine the solubility of PANI and the anticorrosion properties of the coatings. Both the polymeric films acted as smart coatings, releasing anions on demand with different redox behaviors, and CSA-doped PANI exhibited better protective property.

### 3.4. Polyaniline alkyl resin coatings for corrosion inhibition

Alkyd-based coatings are described to exhibit good adhesion, durability, flexibility, and high resistance.<sup>114</sup> Oil-based alkyds are one of the most widely used industrial protective coating materials due to their color stability, low cost, and exceptional weatherability in most environmental situations.<sup>115</sup> Bhanvase *et al.*<sup>116</sup> dispersed PANI and PANI- $\text{CaCO}_3$  nano-composite in alkyd resin in different percentages. The structure and morphology effect of adding PANI and PANI- $\text{CaCO}_3$  nano-composite on the anticorrosion and mechanical properties of alkyd resin were discussed. The results showed that PANI- $\text{CaCO}_3$  resulted in an enhanced adhesion of alkyd resin to metal substrate, an improvement in the impact strength of composite alkyd coatings, and a decreased corrosion rate of PANI- $\text{CaCO}_3$  alkyd resin. These results were attributed to the synergistic effects of PANI and nano-size  $\text{CaCO}_3$ . Marti *et al.*<sup>117</sup> examined the performance of four anticorrosive pigments used in alkyd primer. Very small weight percentages of PANI showed good dispersion in organic solvents such as xylene and organochloride, and provided greater protection to the matrix than other conducting polymers or zinc phosphate. Therefore, it is suggested that PANI is a satisfactory substitute for classical zinc-containing corrosion inhibitors.

### 3.5. Polyaniline used in other coatings and aniline oligomer-derivating polymers for corrosion protection

Yuan *et al.*<sup>118</sup> developed a novel strategy by combining *in situ* chemical oxidative graft polymerization and surface-initiated ATRP to fabricate antibacterial poly(4-vinylaniline)-polyaniline (PVAn-PANI) bilayer coatings for combating biocorrosion by sulfate-reducing bacteria (SRB) in seawater on stainless steel (SS) substrates. Electrochemical results revealed that PVAn-

PANI-modified SS surface conferred corrosion resistance and the desired high barrier ability on SS substrates. With antibacterial properties of quaternized PVAn-PANI bilayers and inherent anticorrosion capability, it was potentially useful for steel-based equipment under harsh marine environments.

PANI, as an anticorrosion agent, was also studied in chlorinated rubber (CR)-based coating system.<sup>119</sup> Sakhri *et al.*<sup>120</sup> discussed the different protective mechanisms of zinc phosphate and polyaniline as pigments in chlorinated rubber paint. They also found that PANI used as an anticorrosive pigment in chlorinated rubber paint at low loading of 1.5 wt% was more efficient than zinc phosphate.

In addition to applying nanostructure of PANI to improve the corrosion protection of coating, aniline oligomer-derivating electroactive polymers with nanostructure, including electroactive epoxy and electroactive polyimide, have attracted much research attention,<sup>121,122</sup> which is a promising area for corrosion protection. For example, Chang *et al.*<sup>123</sup> used nanocasting technique and incorporated the well-defined and conjugated oligoaniline into copolymer backbones to obtain a biomimetic superhydrophobic electroactive polyimide (SEPI) surface structure from a natural *Xanthosoma sagittifolium* leaf, which combined the beneficial properties of specific oligoaniline with desirable polymer properties such as mechanical strength and film-forming ability. Fig. 10 shows the polymeric surface, and the inset picture exhibits the high contact angle. Tafel and Nyquist plots indicated that SEPI coating offered better protection against corrosion than the common coatings.<sup>123</sup>

### 3.6. Protection process and anticorrosion mechanism of polyaniline-based coating

Anticorrosion mechanisms for PANI-based coatings are considered to be quite complex. The morphology and composition of PANI, type of matrix resin, local pH, humidity, galvanic

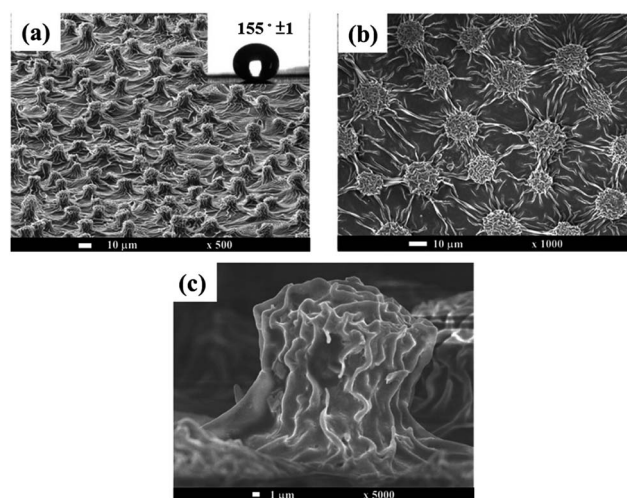


Fig. 10 SEM images of (a) *Xanthosoma sagittifolium* leaf-like superhydrophobic polymeric surface. Inset shows the contact angle of polymeric surface. (b) Top view of polymeric surface. (c) Cross-sectional view of polymeric surface.<sup>123</sup>

activity, corrosive environment, and test method affects the rate of corrosion; all of these factors are regarded as important parameters.<sup>124,125</sup> Fang *et al.*<sup>126</sup> investigated pure PANI coatings deposited on the metal substrates in different solutions by cyclic voltammetry. They summarized the mechanism in which ES had a positive potential to maintain the substrate in a passivation state, and PANI coating could work as a physical barrier to prevent the diffusion of a corrosive media. Thick, compact and excellent adherence was required for pure PANI coating to provide better protection. However, the exact mechanisms for the corrosion processes of PANI-based coatings, which are more complicated than pure PANI, are yet to be fully elucidated.

There are several protective mechanisms of polyaniline material such as passivation mechanism, electric field shielding mechanism, bipolar coating mechanism, adsorption mechanism, anode protection mechanism, and mechanism of dopant ions inhibition. The essence of these mechanisms is the unique oxidation-reduction of polyaniline. These are briefly discussed in the following sections.

**3.6.1. Theory of metal oxide passivation.** The presence of PANI leads to the formation of a dense, protective layer consisting of metal oxide and maintains the metal in a passivation state to protect it from further corrosion. PANI also has the ability to maintain and fast fix the protective layer. In the process of repairing films, PANI is first reduced and then oxidized.


Wessling<sup>127</sup> considered that the formation of the passive film is due to catalytic oxide-redox reactions. He reported the catalytic passivation mechanism of PANI to iron, as shown in Scheme 3. ES was an intermediate in the oxidation of aniline, and LS was the reduction state of polyaniline. The theory pointed out that the dense oxide film kept the metal the passivating region and decreased the corrosion rate of iron.<sup>128,129</sup> In addition, some studies have already confirmed that the oxide film was mainly composed of  $\text{Fe}_2\text{O}_3$  in the outer layer and the  $\text{Fe}_3\text{O}_4$  layer near the iron surface by XPS<sup>130–133</sup> and Raman spectra.<sup>134</sup> Moreover, the oxide film was also found in the scratched part or bare metal area, which explained the superior resistance of polyaniline to pitting and scratch. Moraes *et al.*<sup>96</sup> synthesized a PANI film from phosphate buffer solutions on active metals by the electrochemical method. They assumed that a secondary layer formed by insoluble phosphate also played a key role in the high oxidative capacity of the surface.

**3.6.2. Barrier protection.** Usually, a coating can act as a barrier by separating the metal surface from the corrosive

environment. Beck *et al.*<sup>135</sup> used EIS to investigate the corrosion protection capability of the polymer layer formed from the anodic polymerizations of aniline and pyrrole and their derivatives. Their study suggested that the coating had an obvious inhibition effect when the polyaniline film thickness exceeded 1  $\mu\text{m}$ . This phenomenon was also attributed to the barrier protection of polyaniline. Schauer *et al.*<sup>136</sup> demonstrated the barrier protection mechanism of polyaniline, as shown in Fig. 11. Conductive polyaniline salt helped in the cathode reaction PANI and oxide coating (interface 2), rather than the interface between the metal and oxide coating (interface 3); therefore, anode and cathode reaction were spatially separated, which could stop the pH value of the metal surface from increasing and maintain steel in the passivation state. In this way, PANI improved the anticorrosion ability and protected the metal surface. Hou *et al.*<sup>137</sup> demonstrated that excellent dispersibility of PANI would improve the barrier protection of aggressive ions, and the presence of PANI quite likely enhanced cross-linking and decreased porosity to produce superior protection.

Jain *et al.*<sup>138</sup> presented the mechanism of the electric field effect. The interface between metal and polyaniline yielded an electric field. Electric field and electron transfer were in opposite directions, which could prevent electron transfer from the metal to the oxidant. Conventional organic coating could not form an electric field, which could act as a shield for electron transfer. When the PANI-based coating suffered some defects (scratches or pitting), it still exhibited anticorrosion effects. Radhakrishnan *et al.*<sup>139</sup> intentionally scratched the coating and observed its self-healing property with no rust on the surface even after a long-time exposure to corrosion conditions. They explained these results as the additional cross-linking of PANI. Hence, it is not shielding alone that affects the protection of the metals, and further studies should be conducted to describe this mechanism.

**3.6.3. Complex formation effect.** The main theme of complex formation effect is that the redox reaction, which occurs at the interface between iron and PANI, will generate a complex compound. The oxidation potential of the complex is higher than that of pure PANI, and it promotes the reduction of oxygen, which results in compensating the charge consumed by the dissolution of iron. Complex formation effect can maintain the potential of iron in the passivation region to be stable. Mohammad *et al.*<sup>140</sup> produced PANI-PS core-shell latex

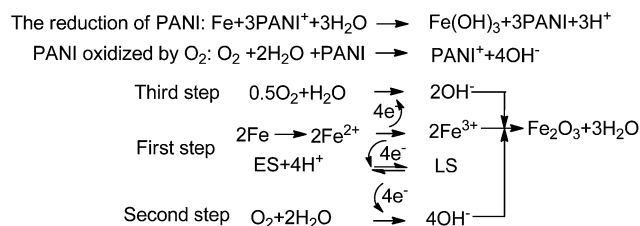

Scheme 3 Description of the catalytic passivation of iron by PANI.<sup>127</sup>

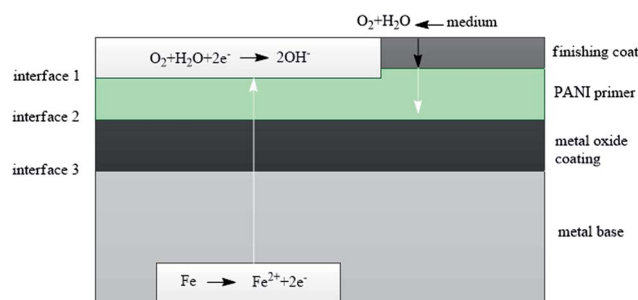


Fig. 11 Barrier protection mechanism of PANI.<sup>136</sup>

microspheres through the adsorption of suspension polymerization method. They assumed the mechanism was one in which PANI and iron generated a complex at the metal interface. During this process the metal was protected and PANI was reduced. By comparing FTIR spectra of the area before and after the corrosion test, Kamaraj and other researchers<sup>113,141–143</sup> considered that the complex film was formed by the interaction between metals and PANI composites.

**3.6.4. Corrosion inhibition effect.** The nitrogen atom of organic amine compounds usually has lone pairs of electrons, which can form coordination bonds with the hollow d orbitals of the metal, such that the molecule adsorbed on the metal surface forms a layer of protective film to protect the metal. Dhawan<sup>144</sup> found that *ortho*-substituted *o*-ethoxy polyaniline exhibited an excellent inhibitive effect, and its anticorrosive efficiency was 8 times more than that of pure polyaniline. The existence of *o*-ethoxyphenol could increase the solubility of aniline. Polar group quaternary ammonium cations and  $\pi$ - $\pi$  bond of phenetidine enabled the polymer to strongly adsorb on the metal surface, forming a uniform capping surface film. Simultaneously, the ethyl in the chain was perpendicular to the metal surface, making the adsorption film more stable. Similarly, Brussic<sup>145</sup> believed that polyaniline, as a corrosion inhibitor for copper, was adsorbed on the surface of copper rather than forming chemical bonds by comparing unsubstituted PANI and poly-*o*-phenetidine derivative.

**3.6.5. Analysis of coating failure mechanism.** The failure mechanism and the main reason for the failure of organic coatings have been widely studied.<sup>146–148</sup> It is well-acknowledged that there are mainly three types of failure situations for anti-corrosive coating. First, bad adhesion between coatings and substrates makes a coating prone to shedding. Second, the coating itself is eroded by acid, alkali, salt or other media, which makes the matrix bare in the corrosion environment and causes its corrosion. Finally, due to the existence of defects in the coating such as pinholes, bubbles, other inclusions, or poor resistance permeability of the coating. Small ions, such as  $\text{Cl}^-$ , can diffuse through the coating, which causes a significant reduction in the resistance of the coating, and thus electrochemical corrosion will occur much faster. In modern industry, taking petroleum as an example, most corrosion is caused by electrochemical corrosion. Numerous cases are due to pinholes, poor resistance of diffusion and permeability. When ions seep into the coating and contact the metal layer, electrochemical corrosion will occur on the surface. Meanwhile, the gas product, such as  $\text{H}_2$  or  $\text{O}_2$ , swells the coating and the surface of the metal flakes off, which makes the coating lose its protection.

As mentioned above, PANI nanostructure-based organic coatings are expected to substantially develop the resistance of coating against three types of failure situations. As depicted in Fig. 12, the nanostructure of PANI composites can enhance the adhesion and mechanical properties of the coating by increasing the interactions between nanoscale composites and targeted substrates. The pathways for  $\text{Cl}^-$ ,  $\text{H}_2\text{O}$  and  $\text{O}_2$  to get to the metal substrate are extended, and thus the ion and gas barrier properties of the coating are improved by PANI nanostructures. Higher specific surface area of nanotubes results in



Fig. 12 Schematic depiction of the mechanism of PANI nanostructure-based coatings.

more contact areas between PANI and matrix polymer; therefore, PANI nanotubes exhibit superior protection to the metal among various PANI nanostructures. In addition to hydrophobicity from the coating with rugged appearance, PANI-based coatings can create a passivation oxide layer for the entire surface and protect the scratched area with self-healing attributes.

## 4. Conclusions and prospects

The oxidation of aniline can produce a variety of nanostructures with different sizes and shapes, including granules, nanofibers, nanotubes and nanospheres. It is concluded that different PANI-based nanostructures can improve the protection of metal by forming passivation oxide and complex layers. By blending with different resin matrices, we could get various anticorrosion mixtures, which could be applied in sundry occasions. The protection processes and anticorrosion mechanisms of PANI-based coatings are complicated due to the wide variations in research processes (PANI-based nanostructure, dispersivity, corrosive environment, doped acid, coating type). PANI nanostructure-based polymer coatings can enhance anticorrosion properties by increasing coating adhesion, producing a high potential of the metal and the self-healing of the engraved area. The significant advantages of nano-PANI anticorrosive coatings lie not only in their easy producing process and eco-friendly, energy-saving and long-term anticorrosion properties, but also in their prospect for preparing self-healing coatings in scratched and pinhole areas, where bare steel surface is exposed to the corrosive ambience. With more comprehension on the extension of the service period of these coatings, remarkable achievements can be made in different industries such as marine, petroleum, construction and energy.

## Acknowledgements

Financial supports from the Guiding fund of Oceanic Interdisciplinary Research of Zhejiang University (2012HY002B), the



Science and Technology Innovation Team of Ningbo (2011B82002), the Natural Science Foundation of Zhejiang Province (Y4110187), and the State Key Laboratory of Chemical Engineering (no. SKL-ChE-12D02) are gratefully acknowledged.

## References

- 1 L. Hao, S. Zhang, J. Dong and W. Ke, *Corros. Sci.*, 2011, **53**, 4187.
- 2 F. U. Renner, A. Stierle, H. Dosch, D. M. Kolb, T. L. Lee and J. Zegenhagen, *Nature*, 2006, **439**, 707.
- 3 A. Stierle, *Science*, 2008, **321**, 349.
- 4 D. G. Shchukin, M. Zheludkevich, K. Yasakau, S. Lamaka, M. G. S. Ferreira and H. Möhwald, *Adv. Mater.*, 2006, **18**, 1672.
- 5 A. Kalendová, P. Kalenda and D. Veselý, *Prog. Org. Coat.*, 2006, **57**, 1.
- 6 H. Gomez, M. K. Ram, F. Alvi, E. Stefanakos and A. Kumar, *J. Phys. Chem. C*, 2010, **114**, 18797.
- 7 N. V. Blinova, J. Stejskal, M. Trchová, J. Prokeš and M. Omastová, *Eur. Polym. J.*, 2007, **43**, 2331.
- 8 M. Yan, C. A. Vetter and V. J. Gelling, *Corros. Sci.*, 2013, **70**, 37.
- 9 V. Annibaldi, A. D. Rooney and C. B. Breslin, *Corros. Sci.*, 2012, **59**, 179.
- 10 N. K. Guimard, N. Gomez and C. E. Schmidt, *Prog. Polym. Sci.*, 2007, **32**, 876.
- 11 S. Palraj, M. Selvaraj, M. Vidhya and G. Rajagopal, *Prog. Org. Coat.*, 2012, **75**, 356.
- 12 Y. Zhu, J. Zhang, Y. Zheng, Z. Huang, L. Feng and L. Jiang, *Adv. Funct. Mater.*, 2006, **16**, 568.
- 13 K. Lee, S. Cho, S. Heum Park, A. J. Heeger, C. Lee and S. Lee, *Nature*, 2006, **441**, 65.
- 14 X. Guo, J. P. Small, J. E. Klare, Y. Wang, M. S. Purewal, I. W. Tam, B. H. Hong, R. Caldwell, L. Huang, S. O'Brien, J. Yan, R. Breslow, S. J. Wind, J. Hone, P. Kim and C. Nuckolls, *Science*, 2006, **311**, 356.
- 15 G. Wu, K. L. More, C. M. Johnston and P. Zelenay, *Science*, 2011, **332**, 443.
- 16 W. Hung, C. Hung, Y. Chang, J. Dai, Y. Li, H. He, S. Chen, T. Huang, Y. Wei, X. Jia and J. Yeh, *J. Mater. Chem.*, 2011, **21**, 4581.
- 17 T. Huang, Y. Su, T. Yeh, H. Huang, C. Wu, K. Huang, Y. Chou, J. Yeh and Y. Wei, *Electrochim. Acta*, 2011, **56**, 6142.
- 18 T. Wang and Y. Tan, *Corros. Sci.*, 2006, **48**, 2274.
- 19 A. A. Hermas, M. Abdel Salam and S. S. Al-Juaied, *Prog. Org. Coat.*, 2013, **76**, 1810.
- 20 G. Gupta, N. Birbilis, A. B. Cook and A. S. Khanna, *Corros. Sci.*, 2013, **67**, 256.
- 21 Y. Li, H. Zhang, X. Wang, J. Li and F. Wang, *Corros. Sci.*, 2011, **53**, 4044.
- 22 A. Mostafaei and F. Nasirpour, *Prog. Org. Coat.*, 2014, **77**, 146.
- 23 V. K. Thakur, G. Ding, J. Ma, P. S. Lee and X. Lu, *Adv. Mater.*, 2012, **24**, 4071.
- 24 W. Jia, L. Su and Y. Lei, *Biosens. Bioelectron.*, 2011, **30**, 158.
- 25 T. G. Kim, H. Shin and D. W. Lim, *Adv. Funct. Mater.*, 2012, **22**, 2446.
- 26 F. Cheng, J. Liang, Z. Tao and J. Chen, *Adv. Mater.*, 2011, **23**, 1695.
- 27 X. Han, C. Chang, L. Yuan, T. Sun and J. Sun, *Adv. Mater.*, 2007, **19**, 1616.
- 28 Y. Cao, L. Xiao, M. L. Sushko, W. Wang, B. Schwenzer, J. Xiao, Z. Nie, L. V. Saraf, Z. Yang and J. Liu, *Nano Lett.*, 2012, **12**, 3783.
- 29 L. Yuan, X. Xiao, T. Ding, J. Zhong, X. Zhang, Y. Shen, B. Hu, Y. Huang, J. Zhou and Z. L. Wang, *Angew. Chem., Int. Ed.*, 2012, **51**, 4934.
- 30 J. Han, L. Li, P. Fang and R. Guo, *J. Phys. Chem. C*, 2012, **116**, 15900.
- 31 C. Chang, C. Weng, C. Chien, T. Chuang, T. Lee, J. Yeh and Y. Wei, *J. Mater. Chem. A*, 2013, **1**, 14719.
- 32 D. Li, J. Huang and R. B. Kaner, *Acc. Chem. Res.*, 2008, **42**, 135.
- 33 S. Bhadra, D. Khastgir, N. K. Singha and J. H. Lee, *Prog. Polym. Sci.*, 2009, **34**, 783.
- 34 Y. Long, M. Li, C. Gu, M. Wan, J. Duval, Z. Liu and Z. Fan, *Prog. Polym. Sci.*, 2011, **36**, 1415.
- 35 A. Pud, N. Ogurtsov, A. Korzhenko and G. Shapoval, *Prog. Polym. Sci.*, 2003, **28**, 1701.
- 36 H. Wang, L. Wang, R. Wang and X. Tian, *J. Mater. Sci.*, 2011, **46**, 1049.
- 37 D. S. Sutar, S. S. Major, R. S. Srinivasa and J. V. Yakhmi, *Thin Solid Films*, 2011, **520**, 351.
- 38 F. I. El-Dib, W. M. Sayed, S. M. Ahmed and M. Elkodary, *J. Appl. Polym. Sci.*, 2012, **124**, 3200.
- 39 S. Chaudhari and P. P. Patil, *Electrochim. Acta*, 2011, **56**, 3049.
- 40 J. Huang and R. B. Kaner, *Chem. Commun.*, 2006, **0**, 367.
- 41 H. D. Tran, J. M. D'Arcy, Y. Wang, P. J. Beltramo, V. A. Strong and R. B. Kaner, *J. Mater. Chem.*, 2011, **21**, 3534.
- 42 J. Stejskal, I. Sapurina and M. Trchová, *Prog. Polym. Sci.*, 2010, **35**, 1420.
- 43 H. D. Tran, D. Li and R. B. Kaner, *Adv. Mater.*, 2009, **21**, 1487.
- 44 N. A. Ogurtsov, Y. V. Noskov, K. Y. Fatyeyeva, V. G. Ilyin, G. V. Dudarenko and A. A. Pud, *J. Phys. Chem. B*, 2013, **117**, 5306.
- 45 H. Qiu, J. Zhai, S. Li, L. Jiang and M. Wan, *Adv. Funct. Mater.*, 2003, **13**, 925.
- 46 F. Lux, *Polymer*, 1994, **35**, 2915.
- 47 I. Sapurina and J. Stejskal, *Polym. Int.*, 2008, **57**, 1295.
- 48 Y. Zhao, J. Stejskal and J. Wang, *Nanoscale*, 2013, **5**, 2620.
- 49 W. Huang, B. D. Humphrey and A. G. MacDiarmid, *J. Chem. Soc., Faraday Trans. 1*, 1986, **82**, 2385.
- 50 F. Wudl, R. O. Angus, F. L. Lu, P. M. Allemand, D. Vachon, M. Nowak, Z. X. Liu, H. Schaffer and A. J. Heeger, *J. Am. Chem. Soc.*, 1987, **109**, 3677.
- 51 K. M. Molapo, P. M. Ndangili, R. F. Ajayi, G. Mbambisa, S. M. Mailu, N. Njomo, M. Masikini, P. Baker and E. I. Iwuoha, *Int. J. Electrochem. Sci.*, 2012, **7**, 11859.
- 52 M. Liu, X. Mao, H. Zhu, A. Lin and D. Wang, *Corros. Sci.*, 2013, **75**, 106.

- 53 L. Pan, H. Qiu, C. Dou, Y. Li, L. Pu, J. Xu and Y. Shi, *Int. J. Mol. Sci.*, 2010, **11**, 2636.
- 54 Y. Wang, H. D. Tran, L. Liao, X. Duan and R. B. Kaner, *J. Am. Chem. Soc.*, 2010, **132**, 10365.
- 55 S. Sathiyarayanan, V. Karpakam, K. Kamaraj, S. Muthukrishnan and G. Venkatachari, *Surf. Coat. Technol.*, 2010, **204**, 1426.
- 56 Y. Liao, V. Strong, W. Chian, X. Wang, X. Li and R. B. Kaner, *Macromolecules*, 2012, **45**, 1570.
- 57 S. Virji, J. Huang, R. B. Kaner and B. H. Weiller, *Nano Lett.*, 2004, **4**, 491.
- 58 J. Stejskal, I. Sapurina, M. Trchová and E. N. Konyushenko, *Macromolecules*, 2008, **41**, 3530.
- 59 T. Pan and Z. Wang, *Microsc. Res. Tech.*, 2013, **76**, 1186.
- 60 D. Chen, Y. Miao and T. Liu, *ACS Appl. Mater. Interfaces*, 2013, **5**, 1206.
- 61 L. A. McCullough, B. Dufour and K. Matyjaszewski, *Macromolecules*, 2009, **42**, 8129.
- 62 J. Chen, D. Chao, X. Lu and W. Zhang, *Mater. Lett.*, 2007, **61**, 1419.
- 63 M. Zhao, X. Wu and C. Cai, *J. Phys. Chem. C*, 2009, **113**, 4987.
- 64 S. Xing, C. Zhao, S. Jing and Z. Wang, *Polymer*, 2006, **47**, 2305.
- 65 C. Weng, Y. Jhuo, C. Chang, C. Feng, C. Peng, C. Dai, J. Yeh and Y. Wei, *Soft Matter*, 2011, **7**, 10313.
- 66 J. Huang and R. B. Kaner, *Angew. Chem., Int. Ed.*, 2004, **43**, 5817.
- 67 C. F. Zhou, X. S. Du, Z. Liu, S. P. Ringer and Y. W. Mai, *Synth. Met.*, 2009, **159**, 1302.
- 68 G. Li, C. Zhang, Y. Li, H. Peng and K. Chen, *Polymer*, 2010, **51**, 1934.
- 69 X. Yang, B. Li, H. Wang and B. Hou, *Prog. Org. Coat.*, 2010, **69**, 267.
- 70 S. Ma, G. Song, N. Feng and P. Zhao, *J. Appl. Polym. Sci.*, 2012, **125**, 1601.
- 71 H. Zhang, J. Wang, X. Liu, Z. Wang and S. Wang, *Ind. Eng. Chem. Res.*, 2013, **52**, 10172.
- 72 L. J. Pan, L. Pu, Y. Shi, S. Y. Song, Z. Xu, R. Zhang and Y. D. Zheng, *Adv. Mater.*, 2007, **19**, 461.
- 73 M. R. Mahmoudian, Y. Alias and W. J. Basirun, *Prog. Org. Coat.*, 2012, **75**, 301.
- 74 P. Deshpande, S. Vathare, S. Vagge, E. Tomšík and J. Stejskal, *Chem. Pap.*, 2013, **67**, 1072.
- 75 A. Vimalanandan, L. Lv, T. H. Tran, K. Landfester, D. Crespy and M. Rohwerder, *Adv. Mater.*, 2013, **25**, 6980.
- 76 C. Weng, Y. Chen, Y. Jhuo, L. Yi-Li and J. Yeh, *Polym. Int.*, 2013, **62**, 774.
- 77 L. Zhang, H. Ma, F. Cao, J. Gong and Z. Su, *J. Polym. Sci., Part A: Polym. Chem.*, 2012, **50**, 912.
- 78 L. Lv, Y. Zhao, N. Vilbrandt, M. Gallei, A. Vimalanandan, M. Rohwerder, K. Landfester and D. Crespy, *J. Am. Chem. Soc.*, 2013, **135**, 14198.
- 79 Y. Zhu, D. Hu, M. X. Wan, L. Jiang and Y. Wei, *Adv. Mater.*, 2007, **19**, 2092.
- 80 C. Li, J. Yan, X. Hu, T. Liu, C. Sun, S. Xiao, J. Yuan, P. Chen and S. Zhou, *Chem. Commun.*, 2013, **49**, 1100.
- 81 A. Prasannan, T. L. B. Truong, P. Hong, N. Somanathan, I. Shown and T. Imae, *Langmuir*, 2010, **27**, 766.
- 82 M. Yang, X. Yao, G. Wang and H. Ding, *Colloids Surf., A*, 2008, **324**, 113.
- 83 C. Peng, K. Chang, C. Weng, M. Lai, C. Hsu, S. Hsu, Y. Hsu, W. Hung, Y. Wei and J. Yeh, *Electrochim. Acta*, 2013, **95**, 192.
- 84 A. Olad and R. Nosrati, *Prog. Org. Coat.*, 2013, **76**, 113.
- 85 E. Akbarinezhad, M. Ebrahimi, F. Sharif, M. M. Attar and H. R. Faridi, *Prog. Org. Coat.*, 2011, **70**, 39.
- 86 M. Kraljić, Z. Mandić and L. Duić, *Corros. Sci.*, 2003, **45**, 181.
- 87 G. S. Goncalves, A. F. Baldissera Jr, L. F. Rodrigues, E. M. A. Martini and C. A. Ferreira, *Synth. Met.*, 2011, **161**, 313.
- 88 M. R. Bagherzadeh, F. Mahdavi, M. Ghasemi, H. Shariatpanahi and H. R. Faridi, *Prog. Org. Coat.*, 2010, **68**, 319.
- 89 H. Gu, S. Tadakamalla, Y. Huang, H. A. Colorado, Z. Luo, N. Haldolaarachchige, D. P. Young, S. Wei and Z. Guo, *ACS Appl. Mater. Interfaces*, 2012, **4**, 5613.
- 90 U. Riaz, S. Ahmad and S. M. Ashraf, *Mater. Corros.*, 2009, **60**, 280.
- 91 J. Xu, P. Yao, Z. Jiang, H. Liu, X. Li, L. Liu, M. Li and Y. Zheng, *J. Appl. Polym. Sci.*, 2012, **125**, E334.
- 92 M. Mumtaz, C. Labrugère, E. Cloutet and H. Cramail, *Langmuir*, 2009, **25**, 13569.
- 93 A. Rahy, T. Rguig, S. J. Cho, C. E. Bunker and D. J. Yang, *Synth. Met.*, 2011, **161**, 280.
- 94 Y. W. Lin and T. M. Wu, *J. Appl. Polym. Sci.*, 2012, **1262**, E123.
- 95 Y. Cao and P. Smith, *Polymer*, 1993, **34**, 3139.
- 96 S. R. Moraes, D. Huerta-Vilca and A. J. Motheo, *Prog. Org. Coat.*, 2003, **48**, 28.
- 97 M. Ochi, K. Takemiya, O. Kiyohara and T. Nakanishi, *Polymer*, 1998, **39**, 725.
- 98 C. Y. Ge, X. G. Yang and B. R. Hou, *J. Coat. Technol. Res.*, 2012, **1**, 59.
- 99 R. S. Jadhav, K. J. Patil, D. G. Hundiware and P. P. Mahulikar, *Polym. Adv. Technol.*, 2011, **22**, 1620.
- 100 B. Belaabed, J. L. Wojkiewicz, S. Lamouri, N. El Kamchi and N. Redon, *Polym. Adv. Technol.*, 2012, **23**, 1194.
- 101 J. Jang, J. Bae and K. Lee, *Polymer*, 2005, **46**, 3677.
- 102 C. Liu, S. Lee, C. Ho, J. Han and K. Hsieh, *J. Phys. Chem. C*, 2008, **112**, 15956.
- 103 X. Zhang, Q. He, H. Gu, H. A. Colorado, S. Wei and Z. Guo, *ACS Appl. Mater. Interfaces*, 2012, **5**, 898.
- 104 F. Chen and P. Liu, *ACS Appl. Mater. Interfaces*, 2011, **3**, 2694.
- 105 U. Riaz, S. M. Ashraf and S. Ahmad, *Anti-Corros. Methods Mater.*, 2008, **55**, 308.
- 106 S. M. Ashraf, S. Ahmad and U. Riaz, *Polym. Int.*, 2007, **56**, 1173.
- 107 G. A. Howarth, *Surf. Coat. Int., Part B*, 2003, **86**, 111.
- 108 T. Gurunathan, C. R. K. Rao, R. Narayan and K. V. S. N. Raju, *Prog. Org. Coat.*, 2013, **76**, 639.
- 109 C. Chen, Y. Kan, C. Mao, W. Liao and C. Hsieh, *Surf. Coat. Technol.*, 2013, **231**, 71.

- 110 F. B. Diniz, G. F. De Andrade, C. R. Martins and W. M. De Azevedo, *Prog. Org. Coat.*, 2013, **76**, 912.
- 111 S. Sathiyarayanan, S. Syed Azim and G. Venkatachari, *Electrochim. Acta*, 2007, **52**, 2068.
- 112 S. Sathiyarayanan, S. Syed Azim and G. Venkatachari, *Synth. Met.*, 2007, **157**, 205.
- 113 J. E. Pereira Da Silva, S. I. Córdoba De Torresi and R. M. Torresi, *Corros. Sci.*, 2005, **47**, 811.
- 114 P. A. Sørensen, S. Kiil, K. Dam-Johansen and C. E. Weinell, *J. Coat. Technol. Res.*, 2009, **6**, 135.
- 115 J. Alam, U. Riaz and S. Ahmad, *Curr. Appl. Phys.*, 2009, **9**, 80.
- 116 B. A. Bhanvase and S. H. Sonawane, *Chem. Eng. J.*, 2010, **156**, 177.
- 117 M. Marti, G. Fabregat, D. S. Azambuja, C. Aleman and E. Armelin, *Prog. Org. Coat.*, 2012, **73**, 321.
- 118 S. Yuan, S. Tang, L. Lv, B. Liang, C. Choong and S. O. Pehkonen, *Ind. Eng. Chem. Res.*, 2012, **51**, 14738.
- 119 A. F. Baldissera, D. B. Freitas and C. A. Ferreira, *Mater. Corros.*, 2010, **61**, 790.
- 120 A. Sakhri, F. X. Perrin, E. Aragon, S. Lamouric and A. Benaboura, *Corros. Sci.*, 2010, **52**, 901.
- 121 C. Weng, C. Chang, C. Peng, S. Chen, J. Yeh, C. Hsu and Y. Wei, *Chem. Mater.*, 2011, **23**, 2075.
- 122 T. Yang, C. Peng, Y. L. Lin, C. Weng, G. Edgington, A. Mylonakis, T. Huang, C. Hsu, J. Yeh and Y. Wei, *J. Mater. Chem.*, 2012, **22**, 15845.
- 123 K. Chang, H. Lu, C. Peng, M. Lai, S. Hsu, M. Hsu, Y. Tsai, C. Chang, W. Hung, Y. Wei and J. Yeh, *ACS Appl. Mater. Interfaces*, 2013, **5**, 1460.
- 124 A. J. Dominis, G. M. Spinks and G. G. Wallace, *Prog. Org. Coat.*, 2003, **48**, 43.
- 125 G. Spinks, A. Dominis, G. Wallace and D. Tallman, *J. Solid State Electrochem.*, 2002, **6**, 85.
- 126 J. Fang, K. Xu, L. Zhu, Z. Zhou and H. Tang, *Corros. Sci.*, 2007, **49**, 4232.
- 127 B. Wessling, *Synth. Met.*, 1997, **85**, 1313.
- 128 B. Wessling, *Adv. Mater.*, 1994, **6**, 226.
- 129 B. Wessling and J. Posdorfer, *Electrochim. Acta*, 1999, **44**, 2139.
- 130 M. Fahlman, S. Jasty and A. J. Epstein, *Synth. Met.*, 1997, **85**, 1323.
- 131 W. Lu, R. L. Elsenbaumer and B. Wessling, *Synth. Met.*, 1995, **71**, 2163.
- 132 T. Yeh, T. Huang, H. Huang, Y. Huang, Y. Cai, S. Lin, Y. Wei and J. Yeh, *Polym. Chem.*, 2012, **3**, 2209.
- 133 Y. Hao, F. Liu and E. Han, *Prog. Org. Coat.*, 2013, **76**, 571.
- 134 G. S. Gonçalves, A. F. Baldissera, L. F. Rodrigues Jr, E. M. A. Martini and C. A. Ferreira, *Synth. Met.*, 2011, **161**, 313.
- 135 F. Beck, V. Haase and M. Schrötz, *AIP Conf. Proc.*, 1996, **354**, 115.
- 136 T. Schauer, A. Joos, L. Dulog and C. D. Eisenbach, *Prog. Org. Coat.*, 1998, **33**, 20.
- 137 W. P. Hou, Y. Liu, Z. Y. Ge and W. Y. Zhao, *Mater. Corros.*, 2013, **64**, 960.
- 138 F. C. Jain, J. J. Rosato, K. S. Kalonia and V. S. Agarwala, *Corrosion*, 1986, **42**, 700.
- 139 S. Radhakrishnan, N. Sonawane and C. R. Siju, *Prog. Org. Coat.*, 2009, **64**, 383.
- 140 Y. M. Abu and K. Aoki, *J. Electroanal. Chem.*, 2005, **583**, 133.
- 141 K. Kamaraj, S. Sathiyarayanan, S. Muthukrishnan and G. Venkatachari, *Prog. Org. Coat.*, 2009, **64**, 460.
- 142 K. Kamaraj, T. Siva, S. Sathiyarayanan, S. Muthukrishnan and G. Venkatachari, *J. Solid State Electrochem.*, 2012, **16**, 465.
- 143 S. de Souza, J. E. Pereira Da Silva, S. I. Córdoba De Torresi, M. L. A. Temperini and R. M. Torresi, *Electrochem. Solid-State Lett.*, 2001, **4**, B27.
- 144 S. Sathiyarayanan, S. K. Dhawan, D. C. Trivedi and K. Balakrishnan, *Corros. Sci.*, 1992, **33**, 1831.
- 145 V. Brusic, M. Angelopoulos and T. Graham, *J. Electrochem. Soc.*, 1997, **144**, 436.
- 146 A. T. Özyılmaz, *Prog. Org. Coat.*, 2005, **54**, 127.
- 147 R. Hasanov and S. Bilgiç, *Prog. Org. Coat.*, 2009, **64**, 435.
- 148 E. Hür, G. Bereket and Y. Şahin, *Prog. Org. Coat.*, 2006, **57**, 149.