



## Dual metal site-mediated efficient C–N coupling toward electrochemical urea synthesis†

Cite this: *J. Mater. Chem. A*, 2023, **11**, 13249

Sourav Paul,<sup>a</sup> Sougata Sarkar,<sup>a</sup> Ashadul Adalder,<sup>b</sup> Amitava Banerjee<sup>b</sup> and Uttam Kumar Ghorai<sup>b</sup>\*

Received 17th February 2023  
Accepted 15th May 2023

DOI: 10.1039/d3ta01011b

rsc.li/materials-a

Electrochemical urea synthesis is a promising technology for carbon utilization. Herein, we report a CoPc–MoS<sub>2</sub> system for promoting urea synthesis by a C–N coupling reaction. Dual metal sites mediate N<sub>2</sub> activation and CO<sub>2</sub> adsorption insertion to produce a urea yield of 175.6 μg h<sup>-1</sup> mg<sub>cat</sub><sup>-1</sup> at –0.7 V vs. RHE.

Urea is a vital compound for societal development, and the high presence of 46% nitrogen (by weight) makes it a major player of the fertilizer industry.<sup>1,2</sup> The growth of the urea based industry is crucial to satisfy the demand of the growing population. Till now, the commercial urea production has depended on the energy intensive reaction between ammonia and carbon dioxide, which utilizes high temperature and elevated pressure conditions (150–200 °C and 150–250 bar).<sup>1</sup> The industrial process requires almost 80% of the globally produced ammonia, produced from artificial nitrogen fixation.<sup>3</sup> However the challenge lies in nitrogen fixation, due to the inert nature of the N≡N triple bond. Therefore industrial ammonia production depends on the century old Haber–Bosch (H–B) process, which demands high temperature and high pressure to break the N≡N triple bond, having a high bond energy of 941 kJ mol<sup>-1</sup>.<sup>4,5</sup> The H–B process consumes 2–3% of the global energy annually and results in significant carbon dioxide emissions.<sup>6</sup> To achieve the goal of a carbon neutral society, a green and clean technology to produce urea under mild conditions is an absolute necessity. An electrocatalytic approach using renewable energy to unify the carbon and nitrogen cycles is a technologically viable and a net zero-carbon emission avenue.<sup>7–10</sup> It is a promising step for the decarbonization of the global economy and a positive move towards

energy sustainability. In recent times, researchers have successfully produced urea using electrocatalysis by a C–N coupling reaction in aqueous media under ambient conditions. Chen *et al.* have coupled N<sub>2</sub> and CO<sub>2</sub> using PdCu–TiO<sub>2</sub> as an electrocatalyst, and the metal alloy system aided in enhancing electronic interaction, chemical adsorption, and active site exposure.<sup>8</sup> Recently, we reported about copper phthalocyanine nanotubes as an efficient electrocatalyst to produce urea.<sup>9</sup> Yuan *et al.* designed a Mott–Schottky heterostructural interface of Bi–BiVO<sub>4</sub>, BiFeO<sub>3</sub>/BiVO<sub>4</sub>, which aids in specific adsorption and activation of CO<sub>2</sub> and N<sub>2</sub> to form urea.<sup>11,12</sup> Apart from experimental reports, theoretical studies were done, which are important with respect to catalyst selectivity and fundamental understanding of reaction mechanisms. Roy *et al.* have carried out the theoretical calculation of a novel non-hazardous metal free catalyst for electrochemical urea synthesis.<sup>13</sup> Zhu *et al.* have systematically studied with DFT about the two-dimensional MBenes (Mo<sub>2</sub>B<sub>2</sub>, Ti<sub>2</sub>B<sub>2</sub> and Cr<sub>2</sub>B<sub>2</sub>) and their capability of coupling of N<sub>2</sub> and CO<sub>2</sub> to form urea.<sup>14</sup>

In spite of the aforementioned catalysts, the progress of the electrochemical process of urea synthesis is hindered significantly due to poor selectivity and low catalytic activity. The reports suggest that the electrocatalyst are synthesized to address the issue of adsorption and activation of reactant molecules, but the C–N coupling process, which is important for urea production has received microscopic attention.<sup>15,16</sup> The challenge exists in byproduct formation, difficulty of separation of urea, low yield and poor faradaic efficiency (FE). In order to overcome the challenge, it is vital to rationally design an electrocatalyst with multiple active sites that enhances the adsorption of gaseous reactants and facilitates the C–N coupling reaction to produce urea. The selection of the catalyst should be made on the following aspects: (i) facile adsorption of the gaseous reactants (N<sub>2</sub> and CO<sub>2</sub>), (ii) facilitation of the carbon dioxide reduction reaction (CO<sub>2</sub>RR) to CO\*, (iii) activity towards the nitrogen reduction reaction (NRR) to NH<sub>2</sub>\*, (iv) the catalyst must have a similar reduction potential range for the NRR and

<sup>a</sup>Department of Industrial Chemistry and Applied Chemistry, Swami Vivekananda Research Center, Ramakrishna Mission Vidyamandira, Belur Math, Howrah 711202, West Bengal, India. E-mail: [uttam.indchem@vidyamandira.ac.in](mailto:uttam.indchem@vidyamandira.ac.in)

<sup>b</sup>Department of Metallurgical and Materials Engineering, Indian Institute of Technology Jodhpur, Jodhpur, Rajasthan 342030, India

† Electronic supplementary information (ESI) available: Experimental section, Fig. S1–S26, and Tables S1 and S2. See DOI: <https://doi.org/10.1039/d3ta01011b>

CO<sub>2</sub>RR, (v) suppression of the hydrogen evolution reaction (HER), and (vi) enhancement of the C–N bond formation.

Prof. Robert and co-workers have shown cobalt phthalocyanine (CoPc) as a highly active, selective and stable electrocatalyst for the electroreduction of CO<sub>2</sub> to CO in a wide pH range (4 to 14).<sup>17</sup> Zhu *et al.* have studied CoPc supported on pyridine functionalized carbon nanotubes (CoPc-py-CNT), which showed superior activity (TOF<sub>CO</sub>: 34.5 s<sup>-1</sup> at -0.63 V *versus* RHE) and high selectivity (FE<sub>CO</sub> > 98%).<sup>18</sup> Furthermore, research reports suggest that transition metal phthalocyanine (MPC) can also play the role of an effective NRR catalyst.<sup>19–23</sup> However, MPC requires a substrate for support, and the substrates are generally carbon based.<sup>19,20</sup> Generally, the substrates are not electrocatalytically active. However, if we select a substrate which possess active sites demonstrates electrochemical activity and provides a framework to support the MPC, it would be highly beneficial to promote urea production *via* C–N bond formation. It is well known that 2D materials (graphene, MoS<sub>2</sub>, TiO<sub>2</sub>, *etc.*)<sup>8,24</sup> can effectively act as a support and participate in electrocatalysis. Prof. Sun and co-workers have shown MoS<sub>2</sub> as an effective NRR electrocatalyst, which showed a FE of 1.17% and ammonia yield of 8.08 × 10<sup>-11</sup> mol s<sup>-1</sup> cm<sup>-1</sup> at -0.5 V.<sup>24</sup> Chou *et al.* have shown that MoS<sub>2</sub> nanosheets can be utilized to tune the NRR as well as HER<sup>25</sup> *via* defect engineering. MoS<sub>2</sub> can act as an effective catalyst for the CO<sub>2</sub>RR.<sup>26</sup> Inspired by the research, which shows that CoPc and MoS<sub>2</sub> are highly active and selective towards the CO<sub>2</sub>RR and NRR in a similar potential range, we designed an electrocatalyst by combining CoPc with MoS<sub>2</sub>, and formed a CoPc–MoS<sub>2</sub> composite system, where MoS<sub>2</sub> nanosheets act as a catalytically active substrate to which CoPc is anchored. The CoPc–MoS<sub>2</sub> electrocatalyst can simultaneously activate and reduce N<sub>2</sub> and CO<sub>2</sub> due to the presence of various active sites and electrochemically produce urea under ambient conditions, which is unexplored by the research fraternity.

In this work, CoPc–MoS<sub>2</sub> composite was prepared by embedding CoPc on MoS<sub>2</sub> nanosheets, which plays the role of efficient electrocatalyst for urea synthesis (Fig. 1a). Even though MoS<sub>2</sub> or CoPc alone showed inferior electrochemical activity, CoPc–MoS<sub>2</sub> showed exuberant electrochemical performance, with a urea yield rate and FE of 175.6 μg h<sup>-1</sup> mg<sub>cat</sub><sup>-1</sup> and 15.12% respectively at -0.7 V *vs.* RHE and it remains similar for five consecutive cycles. The “acceptor–donor” mechanism<sup>21</sup> suggests that the dual metal active sites of ‘Co’ and ‘Mo’ of the CoPc–MoS<sub>2</sub> system have orbitals with appropriate symmetry. So, the vacant d orbitals can accept lone pair electrons of N<sub>2</sub>, and the partially filled d electrons feed electrons back to the N<sub>2</sub> antibonding orbitals. Hence, the N≡N triple bonds are polarized and activated. In the case of single catalytic sites, the empty d orbital of a metal site can accommodate one lone pair electron of the N<sub>2</sub> molecule. To enhance the activation process, the empty d-orbitals of the dual metal sites can pull two lone pair electrons at two ends of the N<sub>2</sub> molecule (Fig. 1b). The polarization of the N<sub>2</sub> molecule facilitates the insertion of the intermediate CO species, produced by the CO<sub>2</sub> reduction at the Mo or Co sites. The Mo sites are preferred active sites for CO<sub>2</sub> reduction due to the localized induced negatively charged surface on the MoS<sub>2</sub> nanosheets. The C–N coupling reaction

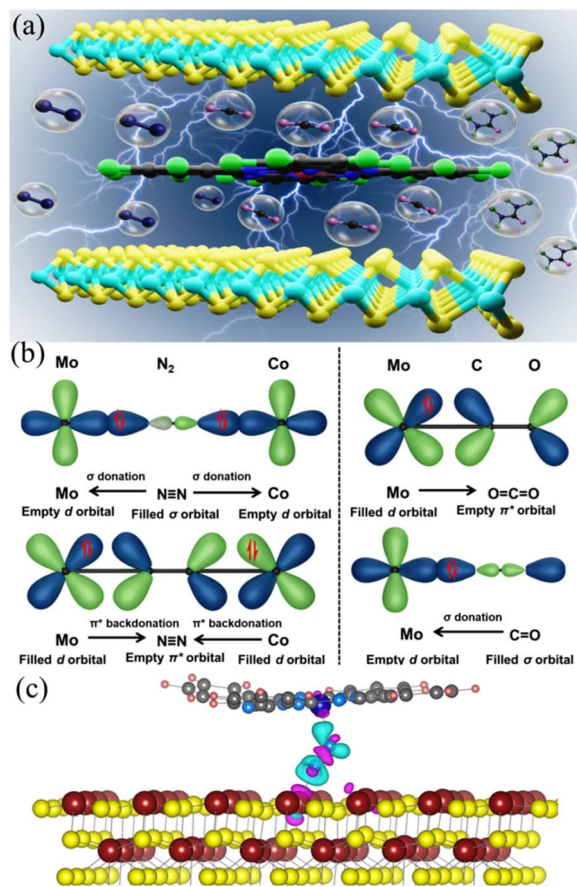


Fig. 1 (a) Pictorial representation of urea synthesis. (b) Schematic diagram showing N<sub>2</sub> bonding to the dual metal site in CoPc–MoS<sub>2</sub>. (c) Charge density difference during N<sub>2</sub> activation by the double metal center in CoPc–MoS<sub>2</sub>. Mo, Co, S, N, C, and H atoms are in maroon, blue, yellow, sky-blue, gray, and pink, respectively. Cyan and magenta isosurfaces (0.01e) show charge depletion and accumulation, respectively.

occurs *via* the CO insertion into the activated N<sub>2</sub> molecule, and the reaction propagates *via* the formation of the triangular shape intermediate state of CONN\* which induces angular strain, and it aids the breaking of the N–N bond and thereafter protonation occurs to form urea as a product.<sup>9,15</sup> The N<sub>2</sub> activation process is further supported by DFT based electronic structure and Bader charge analysis (shown in the ESI†). It has been observed that the dual metal mediated activation process transferred almost 12% more charge to N<sub>2</sub> as compared to single metal center activation. The exchange of charge causes a change in the bond length of N<sub>2</sub> to 1.196 Å for the dual metal center and 1.155 Å for the single metal center compared to the bond length of 1.130 Å for inactive N<sub>2</sub> gas molecules and eventually activate the N<sub>2</sub> molecule. The charge density difference image (Fig. 1c) depicts this charge donation/back-donation to and from N<sub>2</sub> by cyan and magenta isosurfaces.

The isotopic tracing experiment by <sup>1</sup>H-NMR was carried out to unveil the origin of urea formation. The catalyst showed stability for 12 hours without any decrease in electrochemical performance. The catalyst showed brilliant electrochemical

performance due to the following factors: CoPc–MoS<sub>2</sub> interfacial coupling interaction which played an essential role in synergistic stimulation of the Mo-edge sites of MoS<sub>2</sub> and the active site of CoPc toward the urea synthesis, while concurrently protecting the exposed sites from the competing HER.<sup>17,18</sup> The work provides a detailed understanding of the catalytic activity and showed a route to strategically develop an electrocatalyst that can couple N<sub>2</sub> and CO<sub>2</sub> to produce urea. An efficient hydrothermal route was utilized to prepare MoS<sub>2</sub> nanosheets, which played the role of the matrix of the CoPc–MoS<sub>2</sub> composite system in which cobalt phthalocyanine molecules were embedded *via* mechano-chemical blend formation (ESI<sup>†</sup>); the process can be utilized to produce the electrocatalyst on a large scale.

The crystallinity patterns of CoPc, MoS<sub>2</sub> and CoPc–MoS<sub>2</sub> were analyzed by the X-ray diffraction technique as shown in Fig. 2a. In the composite, CoPc was uniformly distributed over the MoS<sub>2</sub> nanosheets, as illustrated by the presence of the characteristics diffraction peaks at (100), (102), (002), (202), (104), (112), and (311), which are well matched with CoPc (JCPDS no. 14-0948),<sup>27</sup> together in unison with the presence of broad diffraction peaks of MoS<sub>2</sub> corresponding to (100), (103), (105) and (110) planes (JCPDS no. 37-1492).<sup>28</sup> Next, high resolution XPS spectra analyses were carried out to probe the electronic properties and chemical composition of CoPc–MoS<sub>2</sub>. In Fig. 2b, the binding energies at 780.2 and 795.6 eV correspond to the Co 2p<sub>3/2</sub> and 2p<sub>1/2</sub> regions, respectively.<sup>21</sup> Meanwhile the peaks detected at 228.7 and 231.9 eV (shown in Fig. 2c) are assigned to the Mo 3d<sub>5/2</sub> and 3d<sub>3/2</sub> electronic states, indicating the presence of the tetravalent state of Mo in CoPc–MoS<sub>2</sub>.<sup>28,29</sup>

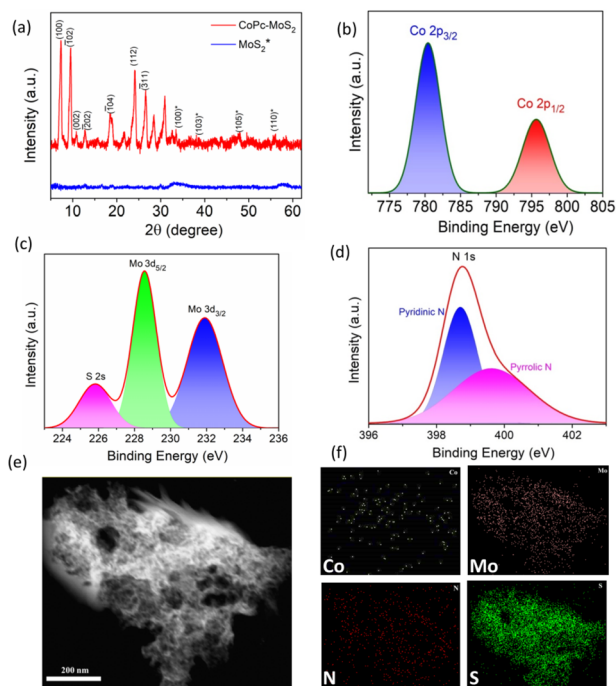


Fig. 2 (a) XRD image, (b–d) high resolution XPS scan of Co, Mo, and N, and (e) TEM image of CoPc–MoS<sub>2</sub>; (f) elemental distribution of Co, Mo, N and S in the CoPc–MoS<sub>2</sub> system.

Similarly, the peaks observed at 161.8 and 162.7 eV (represented in Fig. S2<sup>†</sup>) are assigned to the electronic states of S 2p<sub>3/2</sub> and 2p<sub>1/2</sub> respectively, which represents the divalent state of S in the catalytic system.<sup>28,30</sup> Fig. 2d represents the high-resolution N 1s XPS spectra, and binding energies at 398.7 and 399.6 eV are shown due to the presence of pyridinic nitrogen and pyrrolic nitrogen respectively in CoPc–MoS<sub>2</sub>.<sup>21</sup> In CoPc, the pyridinic nitrogen is bonded to the carbon atom of the phthalocyanine ring while the pyrrolic nitrogen atoms are attached to the central Co atom.<sup>17</sup> The different functional groups of the CoPc–MoS<sub>2</sub> catalyst were identified by using the FTIR spectra (Fig. S3<sup>†</sup>). The TEM imaging reveals that the catalytic surfaces are rough in nature with distinct microporous domains (Fig. 2e). The morphology containing porous regions are expected to provide a greater surface area leading to increase in the exposure of catalytically active sites, thereby enhancing the mass transport.<sup>31</sup> Thus, it leads to efficient N<sub>2</sub> and CO<sub>2</sub> adsorption and electrocatalytic co-reduction to facilitate urea synthesis. The TEM-EDS elemental mapping confirmed that cobalt, molybdenum, sulfur and nitrogen were uniformly distributed in the CoPc–MoS<sub>2</sub> composite (Fig. 2f).

To study the electrocatalytic activity of CoPc–MoS<sub>2</sub>, electrochemical measurements were performed in Ar and (N<sub>2</sub> + CO<sub>2</sub>) purged saturated 0.1 M KHCO<sub>3</sub> electrolyte solution in a H-type

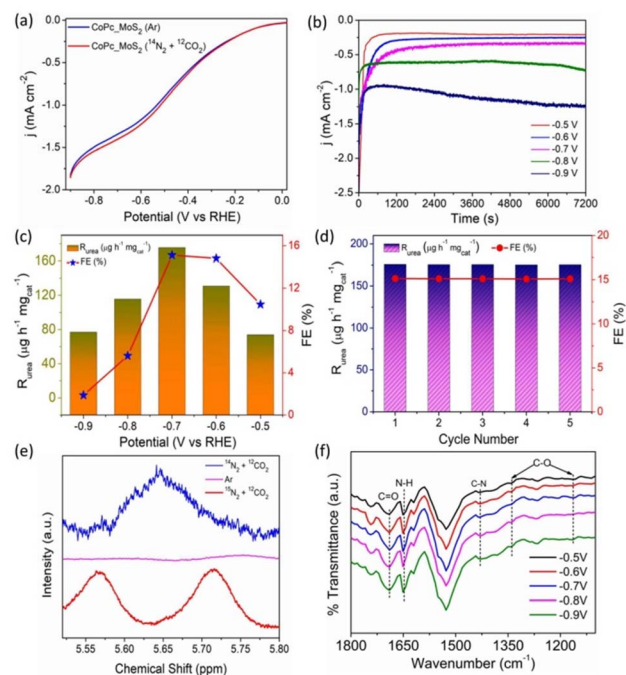


Fig. 3 (a) LSV profile of CoPc–MoS<sub>2</sub> in Ar and N<sub>2</sub> + CO<sub>2</sub> saturated 0.1 M KHCO<sub>3</sub> electrolytes; (b) time dependent current density (*j*) curves for CoPc–MoS<sub>2</sub> at different potentials; (c) urea yield rate and FE with N<sub>2</sub> and CO<sub>2</sub> as the feeding gas at different potentials for CoPc–MoS<sub>2</sub>; (d) the urea yield rate and FE of CoPc–MoS<sub>2</sub> at –0.7 V vs. RHE during recycling tests for five cycles. (e) <sup>14</sup>N and <sup>15</sup>N NMR spectra of electrolytes saturated with <sup>14</sup>N<sub>2</sub> + <sup>12</sup>CO<sub>2</sub>, Ar and <sup>15</sup>N<sub>2</sub> + <sup>12</sup>CO<sub>2</sub> after 20 h of electrolysis. (f) ATR-FTIR spectroscopy experiments of the electrolytes at different potentials during electrocatalytic co-reduction of N<sub>2</sub> and CO<sub>2</sub> using CoPc–MoS<sub>2</sub>.

cell. Fig. 3a shows the LSV curve of CoPc–MoS<sub>2</sub> recorded at 10 mV s<sup>-1</sup> when compared to the Ar saturated electrolyte, there is an increase in current densities in the potential range of -0.5 to -0.8 V (vs. RHE) for N<sub>2</sub> + CO<sub>2</sub> purged electrolyte.<sup>8,9,11</sup> Time dependent chronoamperometry measurements were executed at various potentials in N<sub>2</sub> and CO<sub>2</sub> saturated electrolytes (shown in Fig. 3b). The UV-vis absorption spectrum of the different electrolytes with characteristic absorption of 525 nm at different potentials is shown in Fig. S6† and the maximum absorbance was found at -0.7 V versus RHE. The produced urea was estimated by the diacetylmonoxime (DAMO) method (ESI Experimental section†). The UV-vis absorbance and the related calibration curve for urea quantification are shown in Fig. S4 and S5.† The urea yield rate and corresponding FE in a potential window are displayed in Fig. 3c. CoPc–MoS<sub>2</sub> delivers a maximum urea yield rate and FE of 175.6 μg h<sup>-1</sup> mg<sub>cat</sub><sup>-1</sup> and 15.12% at -0.7 V versus RHE, respectively. It is observed that the urea formation rate rises with increase in negative potential until -0.7 V versus RHE and the rate drops down due to the competitive reaction of H<sub>2</sub> and N<sub>2</sub> on the surface of the electrode. Furthermore, when MoS<sub>2</sub> and CoPc were individually tested, they demonstrated decent electrocatalytic performance, but excellent performance was observed for the CoPc–MoS<sub>2</sub> system (Fig. S16†). The high urea yield rate is attributed to the C–N bond formation through co-reduction of N<sub>2</sub> and CO<sub>2</sub> in the Co metal center, and the Mo edge sites of CoPc–MoS<sub>2</sub>. The vital existence of chemical bonds after the electrochemical synthesis of urea is characterized using the ATR-FTIR technique. Stretching vibrations present at ~1690 and 1165–1334 cm<sup>-1</sup> correspond to the formation of C=O and C–O respectively. The result clearly indicates that CO<sub>2</sub> gas is reduced during the electro-reduction process. The stretching vibration at ≈1431 cm<sup>-1</sup> corresponds to the important C–N bond and confirms the C–N coupling leading to the formation of urea during the electrocatalytic process (Fig. 3f).<sup>8,32</sup>

Recyclability and stability are the two crucial parameters of an electrocatalyst for practical utility. The recycling tests were conducted in a N<sub>2</sub> and CO<sub>2</sub> saturated 0.1 M KHCO<sub>3</sub> solution at -0.7 V potential for five cycles, and the catalyst maintains almost the same urea yield rate in the entire process (Fig. 3d), indicating the stable electroreduction performance of the catalyst. The chemical composition of CoPc–MoS<sub>2</sub> after five consecutive electrocatalytic cycles was investigated by XPS. The high resolution spectra of Co 2p, Mo 3d, and N 1s demonstrate indistinguishable nature with the electrocatalyst before the electrochemical test (shown in Fig. S7–S9†). To further check the stability of the electrocatalyst, a long duration stability test was done at -0.7 V. The catalyst showed an almost stable electroreduction performance without much fluctuation in current density when the electrocatalysis was executed for 12 h (Fig. S10†). Furthermore, to assess the stability of the electrocatalyst, XRD analysis was done post electrolysis, and the result clearly indicates that the structural integrity of the catalyst is maintained (Fig. S11†). In order to find the origin of urea formation, control experiments were done in an Ar (N<sub>2</sub> and CO<sub>2</sub>) saturated electrolyte, and carbon paper without the catalyst, at -0.7 V versus RHE for 2 h. An insignificant amount of urea was

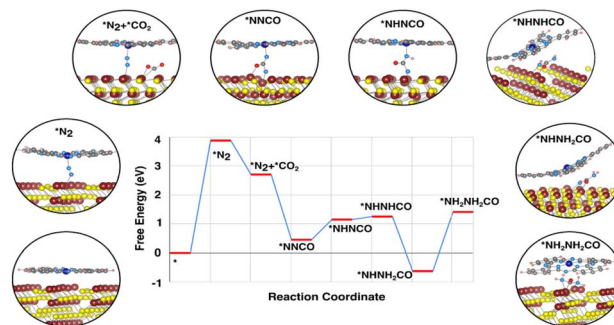


Fig. 4 Free energy profile of the urea synthesis mechanism. Insets show the possible intermediates in the plausible mechanism. Mo, Co, S, N, C, H and O atoms are in maroon, blue, yellow, sky-blue, gray, pink and red, respectively.

detected for all the cases as shown in Fig. S23,† except (N<sub>2</sub> and CO<sub>2</sub>) purged conditions. The selectivity of the catalyst is good, as a negligible amount of hydrazine and a very low amount of ammonia are produced as a side-product (Fig. S19 and S22†). Therefore, the result suggests that CoPc–MoS<sub>2</sub> shows high activity and selectivity towards urea synthesis. The characteristic singlet peak of the formation of urea in <sup>1</sup>H NMR appeared at ≈5.65 ppm when the electrolysis was carried out by purging of <sup>14</sup>N<sub>2</sub> and <sup>12</sup>CO<sub>2</sub> gases and a doublet peak was observed when isotopic <sup>15</sup>N<sub>2</sub> and <sup>13</sup>CO<sub>2</sub> gases were purged during the electrocatalytic reduction process (Fig. 3e). However, no such singlet and doublet were detected when only Ar gas was purged during the electrolysis process, which clearly shows that the urea produced is solely due to the electrocatalytic co-reduction of N<sub>2</sub> and CO<sub>2</sub> gases and not by any contaminants.<sup>8</sup>

The catalytic activity can be estimated with the free energy diagram, which provides a visual representation of the reaction mechanism. The free energy profile (Fig. 4) has identified various possible intermediates and their contribution to the reaction mechanism. In the entire urea formation mechanism, only two uphill reactions have been identified, one is the N<sub>2</sub> activation process and the other is the fourth protonation process, *i.e.* \*NHNH<sub>2</sub>CO to \*NH<sub>2</sub>NH<sub>2</sub>CO formation step. The first uphill step is the rate determining step, where proton/electron transfer does not occur, whereas the second uphill reaction is the potential determining step with an over potential of ~2 V to make all electrochemical steps exothermic. The catalytic origin of the CoPc–MoS<sub>2</sub> system derives from the spatial distribution of the charge in between the dual metal center and N<sub>2</sub> as well as facile formation of the \*NNCO intermediate. The free energy profile depicts that \*NNCO is formed as a result of a favourable downhill reaction. We have also found that, during the formation of \*NNCO, the N≡N triple bond breaks immediately as soon as CO comes close to N<sub>2</sub>. As \*NNCO forms, the fourth protonation step takes place to form urea.

## Conclusions

In summary, CoPc–MoS<sub>2</sub> is theoretically predicted and experimentally confirmed as an active and robust electrocatalyst for

the co-reduction of  $N_2$  and  $CO_2$  gases under ambient conditions. When tested in 0.1 M  $KHCO_3$ , the urea yield rate and FE can reach  $175.6 \mu g h^{-1} mg_{cat}^{-1}$  and 15.12% at  $-0.7 V$  versus RHE, respectively. Impressively, CoPc–MoS<sub>2</sub> exhibits good electroreduction activity and effectively suppresses the hydrogen evolution reaction. This study not only offers us an efficient cost-effective electrocatalyst for high performance  $N_2$  and  $CO_2$  co-reduction under ambient conditions but would open up an exciting new route to explore transition metal dichalcogenide/transition metal phthalocyanine as an efficient catalyst for applications toward urea electrosynthesis.

## Author contributions

UKG conceived the idea and supervised the entire project. SP synthesized the materials and characterised them. SP, SS, and AA performed the electrochemical experiments and analysed the results. SP wrote the original manuscript. SP and AA did the XPS analysis. AB performed the theoretical (DFT) calculations. AB and SP analysed the DFT results. All authors approved the final version of the manuscript.

## Conflicts of interest

There is no conflict of interest.

## Acknowledgements

AA thanks SERB-CRG for the fellowship. SS acknowledges the UGC, Govt. of India for the JRF Fellowship (Scholarship ID: 191620014156). The authors would like to thank IACS Kolkata for providing the instrumentation facilities. The authors acknowledge the financial support from the SERB-Core Research Grant (CRG/2022/009427), WBDSTBT research grant (199 (Sanc.)/ST/P/S&T/6G-12/2018), SERB-Start-up Research Grant (SRG/2022/001377), IIT Jodhpur Seed grant (I/SEED/PRJ//DSN/AB/20220044) and supercomputing facility. AB also acknowledges Dr. Appala Naidu and Department of Metallurgical and Materials Engineering of IIT Jodhpur for software support.

## Notes and references

- 1 F. Barzagli, F. Mani and M. Peruzzini, *Green Chem.*, 2011, **13**, 1267–1274.
- 2 M. Aresta, A. Dibenedetto and A. Angelini, *Chem. Rev.*, 2014, **114**, 1709–1742.
- 3 S. Giddey, S. P. S. Badwal and A. Kulkarni, *Int. J. Hydrogen Energy*, 2013, **38**, 14576–14594.
- 4 A. Adalder, S. Paul and U. K. Ghorai, *J. Mater. Chem. A*, 2023, **11**, 10125–10148.
- 5 A. Banerjee, *Catal. Today*, 2023, **418**, 114079.
- 6 B. H. R. Suryanto, K. Matuszek, J. Choi, R. Y. Hodgetts, H. L. Du, J. M. Bakker, C. S. M. Kang, P. V. Cherepanov, A. N. Simonov and D. R. MacFarlane, *Science*, 2021, **372**, 1187–1191.
- 7 A. Biswas, S. Kapse, R. Thapa and R. S. Dey, *Nano-Micro Lett.*, 2022, **14**, 1–17.
- 8 C. Chen, X. Zhu, X. Wen, Y. Zhou, L. Zhou, H. Li, L. Tao, Q. Li, S. Du, T. Liu, D. Yan, C. Xie, Y. Zou, Y. Wang, R. Chen, J. Huo, Y. Li, J. Cheng, H. Su, X. Zhao, W. Cheng, Q. Liu, H. Lin, J. Luo, J. Chen, M. Dong, K. Cheng, C. Li and S. Wang, *Nat. Chem.*, 2020, **128**(12), 717–724.
- 9 J. Mukherjee, S. Paul, A. Adalder, S. Kapse, R. Thapa, S. Mandal, B. Ghorai, S. Sarkar and U. K. Ghorai, *Adv. Funct. Mater.*, 2022, **32**, 2200882.
- 10 A. Biswas, S. Kapse, B. Ghosh, R. Thapa and R. S. Dey, *Proc. Natl. Acad. Sci. U. S. A.*, 2022, **119**, e2204638119.
- 11 M. Yuan, J. Chen, Y. Bai, Z. Liu, J. Zhang, T. Zhao, Q. Wang, S. Li, H. He and G. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 10910–10918.
- 12 M. Yuan, J. Chen, Y. Bai, Z. Liu, J. Zhang, T. Zhao, Q. Shi, S. Li, X. Wang and G. Zhang, *Chem. Sci.*, 2021, **12**, 6048–6058.
- 13 P. Roy, A. Pramanik and P. Sarkar, *J. Phys. Chem. Lett.*, 2021, **12**, 10837–10844.
- 14 X. Zhu, X. Zhou, Y. Jing and Y. Li, *Nat. Commun.*, 2021, **121**(12), 1–9.
- 15 D. Jiao, Y. Dong, X. Cui, Q. Cai, C. R. Cabrera, J. Zhao and Z. Chen, *J. Mater. Chem. A*, 2022, **11**, 232–240.
- 16 X. Zhang, X. Zhu, S. Bo, C. Chen, M. Qiu, X. Wei, N. He, C. Xie, W. Chen, J. Zheng, P. Chen, S. P. Jiang, Y. Li, Q. Liu and S. Wang, *Nat. Commun.*, 2022, **131**(13), 1–9.
- 17 M. Wang, K. Torbensen, D. Salvatore, S. Ren, D. Joulié, F. Dumoulin, D. Mendoza, B. Lassalle-Kaiser, U. Işci, C. P. Berlinguette and M. Robert, *Nat. Commun.*, 2019, **10**, 1–8.
- 18 M. Zhu, J. Chen, R. Guo, J. Xu, X. Fang and Y. F. Han, *Appl. Catal., B*, 2019, **251**, 112–118.
- 19 S. Murmu, S. Paul, A. Santra, M. Robert and U. K. Ghorai, *Catal. Today*, DOI: [10.1016/J.CATTOD.2022.10.020](https://doi.org/10.1016/J.CATTOD.2022.10.020).
- 20 C. He, Z. Y. Wu, L. Zhao, M. Ming, Y. Zhang, Y. Yi and J. S. Hu, *ACS Catal.*, 2019, **9**, 7311–7317.
- 21 U. K. Ghorai, S. Paul, B. Ghorai, A. Adalder, S. Kapse, R. Thapa, A. Nagendra and A. Gain, *ACS Nano*, 2021, **15**, 5230–5239.
- 22 S. Murmu, S. Paul, S. Kapse, R. Thapa, S. Chattopadhyay, A. Nagendra, S. N. Jha, D. Bhattacharyya and U. K. Ghorai, *J. Mater. Chem. A*, 2021, **9**, 14477–14484.
- 23 J. Mukherjee, A. Adalder, N. Mukherjee and U. K. Ghorai, *Catal. Today*, DOI: [10.1016/J.CATTOD.2022.09.011](https://doi.org/10.1016/J.CATTOD.2022.09.011).
- 24 L. Zhang, X. Ji, X. Ren, Y. Ma, X. Shi, Z. Tian, A. M. Asiri, L. Chen, B. Tang and X. Sun, *Adv. Mater.*, 2018, **30**, 1800191.
- 25 I. Matanovic, K. Leung, S. J. Percival, J. E. Park, P. Lu, P. Atanassov and S. S. Chou, *Appl. Mater. Today*, 2020, **21**, 100812.
- 26 K. Lv, C. Teng, M. Shi, Y. Yuan, Y. Zhu, J. Wang, Z. Kong, X. Lu and Y. Zhu, *Adv. Funct. Mater.*, 2018, **28**, 1802339.
- 27 S. Paul, S. Sarkar, A. Adalder, S. Kapse, R. Thapa and U. K. Ghorai, *ACS Sustainable Chem. Eng.*, 2023, **11**, 6191–6200.
- 28 J. Kibsgaard, Z. Chen, B. N. Reinecke and T. F. Jaramillo, *Nat. Mater.*, 2012, **11**, 963–969.

- 29 X. Wang, H. Feng, Y. Wu and L. Jiao, *J. Am. Chem. Soc.*, 2013, **135**, 5304–5307.
- 30 H. Li, Q. Zhang, C. C. R. Yap, B. K. Tay, T. H. T. Edwin, A. Olivier and D. Baillargeat, *Adv. Funct. Mater.*, 2012, **22**, 1385–1390.
- 31 Y. Li, Z.-S. Wu, P. Lu, X. Wang, W. Liu, Z. Liu, J. Ma, W. Ren, Z. Jiang, X. Bao, Y. G. Li, Z. Wu, P. F. Lu, X. Wang, W. Liu, X. H. Bao, Z. B. Liu, W. C. Ren, J. Y. Ma and Z. Jiang, *Adv. Sci.*, 2020, **7**, 1903089.
- 32 C. Lv, L. Zhong, H. Liu, Z. Fang, C. Yan, M. Chen, Y. Kong, C. Lee, D. Liu, S. Li, J. Liu, L. Song, G. Chen, Q. Yan and G. Yu, *Nat. Sustain.*, 2021, **4**(4), 868–876.