



Cite this: *Environ. Sci.: Adv.*, 2023, 2, 1746

## Assessing sources and fractions of metals associated with environmental plastics: a case study in Lake Como (Italy)<sup>†</sup>

Stefano Carnati,<sup>a</sup> Andrea Pozzi,<sup>a</sup> Davide Spanu,<sup>a</sup> Damiano Monticelli,<sup>a</sup> Roberta Bettinetti,<sup>b</sup> Ginevra Boldrocchi,<sup>b</sup> Luca Nizzetto<sup>cd</sup> and Gilberto Binda<sup>id</sup>\*<sup>ac</sup>

Understanding plastic–metal interactions is paramount to unveil the ecological risks of plastic pollution. Besides including a (variable) amount of metal-containing additives, plastic objects can adsorb metals on their surface in the environment. This work aims at measuring and assessing the possible origin of metals in environmental plastics deposited along the shores of Lake Como (Italy). Samples were characterized through Fourier-transformed infrared spectroscopy (FTIR), scanning electron microscopy (SEM) and water contact angle. Then, the total metal load was analysed by acid digestion. Surface extraction with nitric acid was also performed to detect labile metals and a three-step extraction scheme enabled the determination of physisorbed, carbonate-bonded and organic matter-bonded metals, respectively. Eighteen metals (Al, Ti, V, Cr, Mn, Fe, Co, Ni, Cu, Zn, As, Sr, Ag, Cd, Sn, Ba, Pb and U) were analysed in total. Newly produced plastic items were also analysed as a reference. Our findings revealed that environmental samples retained a higher concentration of metals compared to virgin ones, especially in the loosely bonded acid-extractable fractions, indicating their potential bioavailability. The source of metals on plastics was extremely variable: some metals were predominantly sorbed from the environment (*e.g.*, Mn and Pb), and others were mainly leached from the plastic matrix (Ba, Cu and Ti) or had a mixed origin (Zn, Fe, Sn, Sr and Al). This work shed light on the changes in bioavailability of metals induced by plastic environmental ageing, set baseline values for a freshwater site, and provided insights into the potential bioavailability exerted by metals associated with plastic litter.

Received 31st August 2023  
Accepted 5th November 2023

DOI: 10.1039/d3va00254c

rsc.li/esadvances

### Environmental significance

The interactions between plastic and metals in the environment are of increasing interest owing to the possible environmental implications, such as the change in environmental fate and bioavailability of metals. Metals in plastics can be present as additives (*e.g.*, dyes and catalysts), but can also sorb on plastic surfaces under environmental conditions. In this study, we investigated the content and speciation of different metals in environmental samples of plastic litter and in pristine plastic objects. This permitted the recognition of the likely source of metals in the environmental samples, fostering the investigation of plastic–metal interactions in the environment and shedding light on the potential implications of these processes.

## 1. Introduction

Plastic polymers are used in a great number of products and applications (*e.g.*, industrial, agricultural and technological) owing to their versatility, durability and low cost.<sup>1</sup> The short usage lifespan of most plastic articles in commerce and the

increasing production rates (worldwide production is expected to exceed 33 billion tons by 2050)<sup>2–4</sup> led to the ubiquitous accumulation of plastics in environmental matrices, despite the effort in some regions to improve waste disposal and management.<sup>5,6</sup> Microplastics (MPs), defined as plastic particles having a size <5 mm, are of foremost concern due to their widespread distribution and potential environmental impacts.<sup>7</sup> They have been found in various ecosystems, ranging from water to terrestrial and atmospheric compartments,<sup>8–10</sup> as well as in food products for human consumption.<sup>11–13</sup>

MPs can induce several direct negative effects on the biota, such as entanglement or cellular inflammation following uptake.<sup>14–17</sup> Still, other indirect and subtle effects which can put ecosystems at risk are still not thoroughly understood.<sup>18</sup> As an example, MPs can act as vectors of metals and other inorganic

<sup>a</sup>Department of Science and High Technology, University of Insubria, Via Valleggio 11, Como 22100, Italy

<sup>b</sup>Department of Human and Innovation for the Territory, University of Insubria, Via Valleggio 11, Como 22100, Italy

<sup>c</sup>Norwegian Institute for Water Research (NIVA), Økernveien 94, Oslo 0579, Norway. E-mail: gilberto.binda@uninsubria.it

<sup>d</sup>RECETOX, Masaryk University, Kamenice 753/5, Brno 625 00, Czech Republic

<sup>†</sup> Electronic supplementary information (ESI) available: Tables S1–S5 and Fig. S1–S5. See DOI: <https://doi.org/10.1039/d3va00254c>



chemicals in the environment.<sup>19–21</sup> These particles can, in fact, adsorb and accumulate metals from the surrounding media.<sup>22,23</sup> Furthermore, plastic formulations contain metal-based additives which are added for a variety of purposes, such as plasticizers, flame retardants, antioxidants, pigments and more.<sup>24–26</sup> Many metals exhibit toxicity at low concentrations and can severely threaten organisms at different trophic levels, leading to both acute and chronic effects. Ingestion of metal-enriched plastics can possibly enhance their bioaccumulation.<sup>4</sup>

The sorption–desorption processes of metals on MPs can be affected by various factors. Besides the polymer type and its physicochemical features, a key role in the plastic–metal interaction is played by ageing processes.<sup>27,28</sup> Naturally aged MPs generally show greater sorption of metals compared to pristine polymers.<sup>29–31</sup> Environmental ageing is also observed to increase the leaching of metal-containing additives.<sup>32</sup> Environmental factors such as ultraviolet (UV) radiation exposure, oxidative reactions, mechanical deterioration, and biofouling<sup>23,33</sup> indeed induce polymer embrittlement, increase surface area and enhance polymer wettability. All these alterations enhance the sorption and desorption of metals. Likewise, water physicochemical conditions (*e.g.*, pH, salinity, temperature, redox potential, suspended solids and dissolved organic matter) affect the sorption and desorption processes.<sup>10,34–37</sup> Given the complex framework governing the sorption–desorption processes, unveiling the consequences for the ecosystem is challenging.<sup>35,38</sup>

The analysis of metals on plastic samples collected from environmental matrices can represent an initial step to assess the relevance of this interaction in environmental settings and to help in assessing the environmental risk posed by metal-containing additives leaching from aged plastics, as well as by the metals adsorbed on MPs from the environment. Several approaches have been proposed to examine metals on plastic samples. Acid digestion with strong acid mixtures is still the most employed method: it targets the total content of metals in plastics through the complete dissolution of the plastic polymers. This approach does not allow comparison of the chemical species sorbed on MPs and the metals present in the bulk polymer, limiting the information for an effective bioavailability and exposure assessment.<sup>39–41</sup> Thereby, other methods have been applied to specifically investigate loosely bonded or bioavailable fractions of metals, including single and sequential extractions.<sup>29,42–46</sup>

In our study, we tested a comprehensive analytical approach including total acid digestion, a single-step extraction and a sequential extraction protocol to assess the metal content and fractionation on MP samples. This approach was performed on environmental plastic litter found on the shores of Lake Como (Lombardy, Italy) and, for comparison, on equivalent virgin plastic objects obtained from local grocery stores. The comparison between virgin and environmental samples helped to size the metal pool originally present in the plastic formulations and, by comparison, the potential changes in (bio) availability (*i.e.*, the release from the polymer matrix or the sorption from the environment). In addition, we investigated the role of plastic properties and environmental ageing in the

changes in metal availability through their characterization using Fourier-transformed infrared spectroscopy (FTIR), scanning electron microscopy (SEM) and water contact angle. This study focused on a freshwater body since freshwater ecosystems have recently been reported as sinks for MPs, but they are still limitedly studied concerning the interaction of MPs and metals.<sup>39,47–49</sup> Data associated with these environments are therefore limited and fragmented.<sup>50,51</sup>

## 2. Materials and methods

### 2.1 Study area

The study area for the collection of environmental plastic and water samples encompassed Como shores (Italy). This site is located at the end of the southwestern branch of Como Lake: a glacial, meso-eutrophic lake in northern Italy.<sup>52,53</sup> Water chemistry in Lake Como is dominated by  $\text{Mg}^{2+}$ ,  $\text{Ca}^{2+}$  and  $\text{HCO}_3^-$  ions.<sup>54</sup>

In this part, the lake has no effluents. Two main streams (Valduce and Cosia), instead, drain from Como city to the lake. The main sources of plastic litter in the Bay were observed to be direct littering on the beaches and longitudinal transport of floating litter from the northern part of the lake induced by local winds.<sup>55</sup> We collected plastic litter samples around Villa Geno (45.823° N, 9.076° E, Fig. 1) since this site was observed to be a major hot spot of plastic litter in the area.<sup>55</sup>

### 2.2 Plastic sample collection and pre-treatment

In this study, environmental and pristine macroscopic plastic objects and fragments (>5 mm) were used to generate simulated MPs after a grinding process. This approach enables the analysis of the abundant and homogenous sample in the MP size range, which in turn opens the way to analyse both the total amount of metals and the fractionation through different extraction protocols from a single sample batch.<sup>46</sup>

We manually collected macroscopic plastic fragments characterized by a visible advanced ageing state. Sample collection was done wearing nitrile gloves and the samples were stored in virgin polyethylene (PE) bags to avoid metal contamination. Once in the laboratory, environmental samples were sorted according to the object category of litter (*e.g.*, bottles, glasses, caps, toys, packaging), colour and polymer type. The latter was assigned after visual sorting in case recycling codes were still visible and validated through FTIR analysis (see Section 2.3).

Samples of virgin plastics were obtained from new plastic objects representing the same categories, colours, and polymer types as the environmental samples. These samples were analysed in order to: (i) evaluate the concentrations of metals voluntarily used as additives in new objects during manufacturing, and (ii) control potential contamination during sample processing.

All plastic samples (virgin and environmental) were in fact processed in the same way. They were first rinsed with ultrapure water to remove other solids loosely attached to the surface (*e.g.*, sand) and air-dried for approximately 24 hours. Samples were then cut into smaller pieces, ground with a commercial mixer





Fig. 1 Location map of Como Bay (panel a), as part of Lake Como (panel b), and Italy (panel c). The sampling site of environmental samples (Villa Geno) is highlighted with a blue cross. Sources: Google satellite images overlapped with the official state cartography (scale 1 : 25.000) provided by IGMI (Italian Army's Geographic Supporting Office).

with stainless-steel blades, and sieved to <2 mm. This treatment yielded enough homogeneous samples in the form of fragments with the size scale of MPs (<5 mm), needed for the following analytical steps. In total, 3 samples of PE, 3 of polypropylene (PP) and 3 of polyethylene terephthalate (PET) were prepared for metal analysis. For every polymer category, one pristine and two environmental samples were analysed (Table 1).

### 2.3 Plastic sample characterization

Samples were analysed for specific surface functional groups with a Thermo Scientific™ (Waltham, MA, USA) Nicolet™ iS™ 10 attenuated total reflectance FTIR spectrometer, in order to:

(i) determine the polymer composition and (ii) assess the

changes of surface functional groups induced by environmental ageing and biofilm development. Thirty-two scans were performed for every sample in the 4000–650  $\text{cm}^{-1}$  spectral interval, with a resolution of 0.482  $\text{cm}^{-1}$ . A background spectrum was recorded prior to every measurement. All collected FTIR spectra were smoothed using the Savitzky–Golay filter (30 points of the window) and normalized on the maximum absorbance peak using Origin 2018 software (OriginLab Corporation). A range of indexes were calculated for a quantitative comparison of FTIR data. The following generalized equation was applied for calculating the indexes of different functional groups:

$$I_i = \frac{A_i}{A_{\text{ref}}}$$

Table 1 List of samples and their characteristics, including their type (virgin or environmental), object category, colour, and polymer type

Polymer type	Sample label	Type of sample	Item	Colour
PE	PEvir1	Virgin	Cap	Blue, green, and white
	PEenv2	Environmental	Cap	Blue, green, and white
	PEenv3	Environmental	Vase	Grey
PP	PPvir1	Virgin	Cup	Transparent
	PPenv2	Environmental	Cup	Transparent
	PPenv3	Environmental	Cup	White
PET	PETvir1	Virgin	Bottle	Transparent
	PETenv2	Environmental	Bottle	Transparent
	PETenv3	Environmental	Bottle	Transparent



in which  $I_i$  represents the index for the surface group analysed, namely the carbonyl group at  $1715\text{ cm}^{-1}$ , hydroxyl groups at  $3500\text{ cm}^{-1}$ , amides at  $1650\text{ cm}^{-1}$ , and polysaccharides at  $1040\text{ cm}^{-1}$ .  $A_i$  is the absorbance value at the specific wavelength, whereas  $A_{\text{ref}}$  stands for the absorbance values at specific reference bands selected for the different polymer types: the C–H band at  $1465\text{ cm}^{-1}$  for PE,<sup>56</sup> the reference peak at  $1892\text{ cm}^{-1}$  for PP,<sup>57</sup> and the band absorbing at  $721\text{ cm}^{-1}$  for PET.<sup>58</sup>

In addition to FTIR spectra, SEM images were collected to examine the surface micromorphology using a Philips® (Netherlands) field emission gun-scanning electron microscope (FEG-SEM), with a 20 keV beam under high vacuum conditions. Before SEM analysis, samples were made more conductive by covering them with a gold layer using a Cressington (UK) 108 auto vacuum sputter coater.

Static water contact angles were also measured to assess the surface charge of plastic samples. Briefly, 5  $\mu\text{L}$  of ultrapure water was deposited on the sample surface and pictures were collected *via* a smartphone camera system. Then, contact angles were processed using ImageJ software.<sup>59</sup>

#### 2.4 Metal analyses

The total metal concentration in all plastic samples was assessed by acid digestion.<sup>44,60</sup> Approximately 60 milligrams of the prepared sample were weighed and put into a Teflon vessel, where 4 mL of ultrapure concentrated nitric acid were added. The vessels were placed in a microwave oven (Milestone ETHOS One), with a 10 minute initial heating up to  $180\text{ }^\circ\text{C}$  and a following isotherm of 15 minutes. After digestion, the solutions were transferred into LDPE bottles, diluted with ultrapure water and stored at  $4\text{ }^\circ\text{C}$  in a refrigerator.

Surface extraction with ultrapure nitric acid ( $\text{HNO}_3$ ) 2% v/v in an ultrasonic bath for 10 minutes at 120 W was also applied to desorb all loosely bonded metals.<sup>27</sup> In addition, a recently proposed sequential extraction scheme was performed on the samples to analyse three different metal fractions on MPs: (i) the physisorbed and readily soluble fraction of metals with ammonium nitrate 1 M;<sup>61</sup> (ii) the acid-soluble fraction of metals with acid acetic 0.1 M; and (iii) the oxidizable and bonded to organic matter fraction of metals with hydrogen peroxide 30% v/v. A detailed description of this methodology is available elsewhere.<sup>46</sup>

Solutions obtained by acid digestions and different extraction methods were analysed through inductively coupled plasma – mass spectrometry (ICP-MS Thermo Scientific™ Icap-Q, USA) for the detection and quantification of 18 metals, namely: aluminium (Al), titanium (Ti), vanadium (V), chromium (Cr), manganese (Mn), iron (Fe), cobalt (Co), nickel (Ni), copper (Cu), zinc (Zn), arsenic (As), strontium (Sr), silver (Ag), cadmium (Cd), tin (Sn), barium (Ba), lead (Pb) and uranium (U).

#### 2.5 Water sample collection and chemical analysis

Along with the collection of plastic items, lake surface water was sampled to analyse the physicochemical conditions and the metal concentration in the water phase, potentially affecting sorption processes. Physicochemical parameters (pH, temperature, and electrical conductivity) were measured *in situ* using handheld

probes (HI 9025 pH meter and HI 9033 conductivity meter, HANNA Instruments, Italy). For metal analyses, water samples were directly filtered *in situ* and stored in pre-cleaned LDPE bottles (Nalgene®).<sup>62</sup> These bottles were kept in the dark and transported to the laboratory, where samples were stored in a refrigerator at  $4\text{ }^\circ\text{C}$ . The analysis of trace elements was done *via* ICP-MS, as explained in Section 2.3. Before ICP-MS analysis, samples were acidified by the addition of ultra-pure distilled nitric acid reaching a final concentration of 2% v/v. Samples were analysed in three replicates, monitoring the relative standard deviation (RSD) to be below  $\pm 5\%$ . Major anions and cations ( $\text{F}^-$ ,  $\text{Cl}^-$ ,  $\text{Br}^-$ ,  $\text{NO}_3^-$ ,  $\text{PO}_4^{3-}$ ,  $\text{SO}_4^{2-}$ ,  $\text{Li}^+$ ,  $\text{Na}^+$ ,  $\text{NH}_4^+$ ,  $\text{K}^+$ ,  $\text{Mg}^{2+}$ , and  $\text{Ca}^{2+}$ ) were instead determined through ion chromatography (Eco IC Metrohm, Switzerland). More details concerning water sampling methods, analysis and QA/QC protocols are reported elsewhere.<sup>63</sup>

#### 2.6 Reagents, QA/QC protocols and data analysis

Quality control (QA/QC) measures were applied to ensure reliable and accurate measurements of metals. First, all operations were carried out under a linear flow hood to avoid airborne contamination (aura HZ72T BIOAIR, Italy). The solutions were prepared from analytical grade reagents and ultrapure water (obtained by a Sartorius Arium® mini, Germany; resistivity:  $18.8\text{ M } \Omega\text{ cm}$ ; TOC:  $<5\text{ ppb}$ ). Ultrapure nitric acid 67–69% was produced through purification of analytical grade acid (Carlo Erba reagents, Italy) using sub-boiling distillation in a Milestone (USA) DuoPur system.<sup>64</sup> Ammonium nitrate solution was prepared by dissolution of its crystalline salt (Carlo Erba reagents, Italy). Acetic acid solution was obtained from dilution of glacial acetic acid (Carlo Erba reagents, Italy), while hydrogen peroxide 30% v/v was purchased as it is (Sigma-Aldrich, USA). Before use, all the lab containers were cleaned with a detergent solution (NALGENE® L900) first, then soaked in a 2% nitric acid bath, washed with ultrapure water, and lastly air dried under a laminar flow hood. To assure precision and accuracy in the quantification during ICP-MS analysis, a multi-element standard was used for external calibration. This was prepared by dilution of Sigma-Aldrich (USA) multi-elemental standard. Analytical blanks were employed to take any source of possible contamination into account. To avoid cross-contamination during the grinding process, the blender was rinsed twice with ultrapure water between any sample processed.

All the measurements were performed in replicates to determine their uncertainty. Method detection limits (MDLs) were estimated using method blanks: they were calculated as the mean determined concentration plus three times the standard deviation of a set of method blanks. During data analysis, values which were below the method detection limits were substituted with MDL/2 value.<sup>65</sup>

The final data were reported as  $\mu\text{g}$  of the extracted metal by a unit of volume ( $\text{cm}^3$ ) of the dry sample. This method of displaying results allowed all values coming from different polymer types to be compared with each other. To this end, reference density values chosen for weight-to-volume conversions were  $0.94\text{ }\mu\text{g cm}^{-3}$  for PE,  $0.90\text{ }\mu\text{g cm}^{-3}$  for PP and  $1.41\text{ }\mu\text{g cm}^{-3}$  for PET.<sup>66</sup>



To evaluate the available fractions (extractable from the surface) against the total metal quantities in different samples, extraction ratios were calculated as follows:

$$\text{Extraction ratio [\%]} = \frac{[M]_{\text{surface}}}{[M]_{\text{total}}} \times 100$$

where  $[M]_{\text{surface}}$  is the concentration of the extracted metal with the surface extraction protocol, whereas  $[M]_{\text{total}}$  represents the total concentration of the same metal determined through the acid digestion procedure.

Descriptive statistics (25<sup>th</sup>–75<sup>th</sup> percentiles, median and maximum) were applied to summarize the dataset regarding acid digestion, surface extraction and sequential extractions for all samples. Calculations and other statistics (non-parametric Mann–Whitney test) were performed with Origin 2018 software (OriginLab Corporation, Northampton, MA, USA).

### 3. Results and discussion

#### 3.1 Total and extractable concentrations of metals from plastic samples

The total load of metals in the samples showed pronounced variability with concentrations ranging from values greater than 1000  $\mu\text{g cm}^{-3}$  to values below the limit of detection (Table S1 and Fig. S1†). Specifically, metals such as Sn, Fe, Al, Ba and Zn were detected at the highest concentrations (average values ranged from  $\sim 10 \mu\text{g cm}^{-3}$  to  $\sim 200 \mu\text{g cm}^{-3}$ ), Mn, Cu, Sr and Ti exhibited one order of magnitude lower concentrations (average values from  $\sim 1 \mu\text{g cm}^{-3}$  to  $\sim 10 \mu\text{g cm}^{-3}$ ), while Ni, Pb, As, Cr, Ag, Co, V, Cd and U were less abundant (averagely below  $1 \mu\text{g cm}^{-3}$ , Table S1†). This heterogeneous trend was also observed in virgin samples: no statistically meaningful differences in the total metal concentration were observed between environmental and pristine samples for most of the analysed elements (Mn and Pb were the only two exceptions, Fig. S1†). The high total concentrations of several metals in virgin samples indicate the abundant use of inorganic and metal–organic additives and fillers in the formulation of plastic items (see detailed discussion in Section 3.4).

High variance of total metals in environmental plastics was reported for other freshwater settings.<sup>39,49</sup> Variance in metal content can stem from sample polymer type and level of ageing, environmental conditions of the sampling areas and extraction methods used for metal quantification. This high variance also hampers a proper comparison with our data. These outcomes confirm the great chemical heterogeneity of plastic materials, as well as the complexity of the interactions with other chemicals they are exposed to in the environment. The interpretation of the total digestion data from environmental plastic, therefore, should be carefully investigated in order to avoid potential overestimations of the environmental exposure and bioavailability.

The extraction ratios measured through data from the surface extraction ( $\text{HNO}_3$  2%, targeting loosely bound metals on the surface of the objects) revealed a clearer trend. Environmental samples of every polymer displayed, in fact, generally higher extraction ratios compared to virgin samples for the corresponding metals, with significant differences for 8 of the



Fig. 2 Average extraction ratios of the labile metals associated with plastic samples. Panel (a) shows the differences in environmental and virgin samples, while panel (b) shows the differences among different polymer types. Significantly different data ( $p < 0.05$ ) after Mann–Whitney test are indicated by an asterisk.

analysed metals (*i.e.*, Sn, Al, Mn, Pb, Ti, Co, V and U, Fig. 2a). Considering the environmental samples, Sn, Pb, Mn and U were the metals desorbing from the surface in a greater quantity relative to their total content (extraction ratios ranged from 30% to 90%). By contrast, other metals yielded  $<10\%$  in extraction ratios (*i.e.*, Fe, Cr, Ag, Cu, Sr and Zn), indicating that they were likely more present (and more strongly retained) in the polymer matrix, most probably already in origin. The significant increase of extraction ratios of environmental samples compared to virgin ones can be potentially related to the increased leaching of metal additives after polymer ageing: experimental evidence in the laboratory highlighted that the polymer ageing process (after UV irradiation) increased extraction ratios of different plastic types, reaching values up to the 75%.<sup>67</sup>

Ni, Cd and Ba showed instead (not statistically significant) higher values of extraction ratios for virgin plastics in comparison to environmental samples. This observation coincided however with extremely low concentrations of these elements in both the total digestion and the direct extraction of several pristine MPs (Table S1†), which may more easily lead to an overestimation of the extraction ratios. Considering the absolute values of surface extractions with  $\text{HNO}_3$  2% (Table S2 and Fig. S2†), in fact, environmental samples show a significantly higher absolute concentration of these metals in comparison to virgin samples.

#### 3.2 Metal fractionation on plastic samples

Sequential extractions provided further insights concerning the fractions of labile metals, helping in discriminating the possible sources of the metals on plastic samples.



The discussion of metal fractionation here is limited to the 11 more abundant analysed elements since the others (*i.e.*, Ag, As, Cd, Co, Cr, V, U) presented values below the detection limits for more than 50% of the samples, hampering a significant comparison of data. Expectedly, as for other extractions, there were marked differences between environmental and pristine plastic samples (Fig. 3 and Table S2†). Virgin samples yielded lower concentrations of metals in all three extraction steps (Fig. 3a) in comparison to environmental samples (Fig. 3b) for most of the analysed elements, with the exceptions of Cu and Zn. Results were in line with the concentrations obtained from surface extraction.

The fractionation pattern of the metals differed between virgin and environmental samples, too. In the case of virgin samples, the second extraction step (acetic acid 0.1 M) provided higher quantities for most metals (Mn, Cu, Pb and Ti were the only exceptions), whereas the third extraction step (hydrogen peroxide 30% v/v) yielded the lowest amount (or below detection limits), with the only exception of Ti. Environmental samples showed, instead, several changes in metal fractionation. For example, the third extraction step produced a significant increase in the case of Sn, Fe, Al and Zn: this effect could be due to the sorption of metals in the organic matter (or biofilms) present on the surface of plastics obtained from the environment, and absent on pristine plastics.<sup>68–70</sup> In addition, other metals such as Ni and Sr showed higher concentrations in the first step (which extracted metals bonded through more labile forms of bonding compared to the other steps). For Al, Fe, Zn and Pb instead the extraction step with acetic acid yielded the

highest quantity of metals. These results were in line with previous studies, indicating a pH-dependent leaching of these metals.<sup>25,27,71</sup> The high variability of changes in metal fractionation proves again that plastic–metals interactions are complex processes, both dependent on metal properties (*e.g.*, the source as additive or the sorption in the environment and its chemical properties) and the environmental conditions.

### 3.3 The role of polymer type and ageing in regulating plastic–metal interactions

The differences observed between environmental and pristine samples indicate that MP environmental ageing processes are key in defining metal sorption–desorption equilibria, confirming the results of other case studies investigating MP–metal interactions.<sup>72–76</sup> The physicochemical characterization of the plastic samples helped in shedding light on the factors affecting sorption–desorption processes.

FTIR analysis guided the identification of the polymers composing the environmental and pristine samples (*i.e.*, PE, PP and PET, Fig. S3†) through the analysis of the fingerprinting absorption bands (Table S3†). These polymers are indeed the most used in everyday items (PE and PP are the two most manufactured types worldwide), as also found in other settings.<sup>77</sup> In addition, the abundance of PE and PP is representative of beached litter, which is generally composed of low-density polymers, which float on water and are transported by surface currents and winds.<sup>55</sup>

The FTIR spectra of environmental samples also showed some clear changes in functional groups induced by the environmental ageing of polymers in comparison to the virgin samples.<sup>78</sup> The changes in the indexes for specific aging bands are shown in Fig. 4: the main variations were observed in the regions of hydroxyl ( $3600\text{--}3000\text{ cm}^{-1}$ ) and carbonyl groups ( $1300\text{--}1000\text{ cm}^{-1}$ ), confirming the superficial oxidation due to a series of co-occurring environmental processes, such as UV exposure, atmospheric oxygen and thermal effects. This is particularly evident for polymers mainly composed of aliphatic chains like PE and PP. These changes in functional groups on the surface of polymers may affect metal sorption, with the potential development of either coordination complexes or non-covalent interactions.<sup>2,38,79</sup> Another process that can modify polymer FTIR spectra is biofouling.<sup>68,69</sup> The presence of a biofilm on the environmental samples can be inferred from characteristic absorption peaks indicative of either proteins ( $1650\text{ cm}^{-1}$  and  $1550\text{ cm}^{-1}$  regions, respectively for amide I and II stretching), or polysaccharides ( $1040\text{ cm}^{-1}$  band of C–O stretching).<sup>81</sup> These bands were noticeable in 2 out of 6 environmental samples (PEenv3 and PPenV2, respectively), while clearly lacking in virgin samples. These two samples, in fact, showed higher concentrations of Al, Mn, Fe and Pb compared to most of the other pristine and environmental samples in the most labile fractions (steps 1 and 2, Table S2†). This organic layer may play a pivotal role in the sorption of metals from the environment and in the potential release of additives. The different surface groups may induce chemical sorption of several metals (*e.g.*, through complexation with extracellular



Fig. 3 Speciation of the labile metals obtained with the three-step extraction scheme. Average values of the three metal fractions distinguished for virgin (panel a) and environmental (panel b) samples are reported. Results for Ag, As, Cd, Co, Cr, V, and U are not shown since more than 50% of the samples were below MDL.



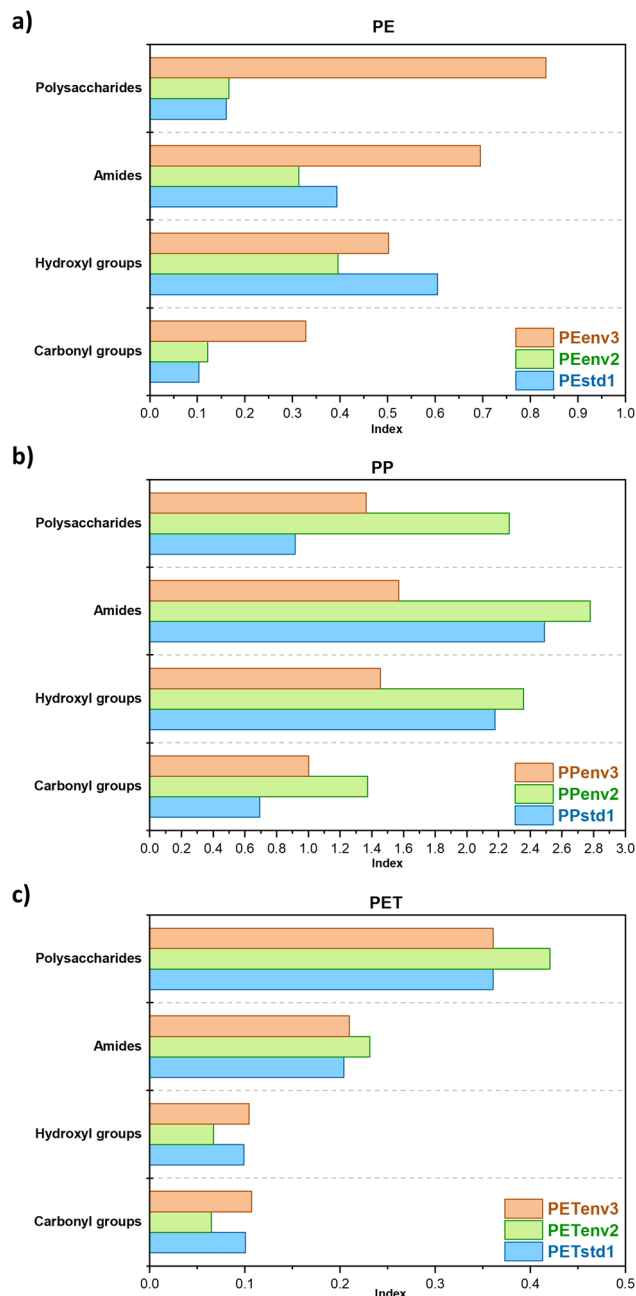


Fig. 4 Indexes of IR bands for the different polymer types: PE (a); PP (b); PET (c). Environmental samples (env) and virgin samples (vir) are displayed. Indexes referred to amides ( $1650\text{ cm}^{-1}$ ), polysaccharides ( $1040\text{ cm}^{-1}$ ), hydroxyl ( $3500\text{ cm}^{-1}$ ) and carbonyl groups ( $1715\text{ cm}^{-1}$ ).

polysaccharides), while microorganisms may also actively absorb metals from water in solution.<sup>68,69,82–84</sup> Biofilms may mediate metal additive release from plastic, too.<sup>85</sup> Unfortunately, the lack of a quantitative analysis of biofilm coverage on plastics hampered a clear assessment of this process in our study.

Beyond surface functional groups, environmental ageing of plastic affected the surface micromorphology of the generated MPs. SEM images (Fig. 5) showed, in fact, evident differences between the images of virgin samples and environmental



Fig. 5 SEM images of one virgin (a, c, and e) versus one environmental (b, d, and f) sample for every polymer type (i.e., PE, PP and PET) at various magnifications.

samples, regardless of the type of polymer composing the sample. The surfaces of pristine samples appeared smooth and homogeneous, with limited irregularities, whereas those of environmental samples were typically rugged, and wrinkled, with several evident pits and cracks (Fig. S4†). These changes may indeed increase both the sorption of metals from the environment and the release of metal additives due to the increase of the specific surface area of plastic fragments, as already largely documented in prior studies.<sup>23,27,49,86</sup> Another noteworthy feature of environmental samples was the presence of several organisms composing the biofilm community on the surface of environmental samples: the residuals of diatom frustules are evident in some of the samples (Fig. 5b and f), as well as cocci and filamentous-shaped cells colonizing the surfaces (shown in Fig. 5d). These organisms can actively absorb metals in their cytoplasm and entrap ions in their extracellular matrices, favouring the sorption from the environment.<sup>87</sup>

Finally, the effects of ageing on the surface properties of plastic samples are corroborated by the water contact angle measurements (Fig. S5†). The values of contact angle are influenced by the polymer type in virgin samples: PP and PE samples are hydrophobic, while PET is slightly hydrophilic (i.e., contact angle  $<90^\circ$ ). All the environmental samples, however, showed a decrease in contact angle values of at least  $10^\circ$  in comparison to the virgin sample of the same polymer, regardless of the polymer type. This confirms the effect of ageing and biofouling, making the surface of plastics richer in polar surface



functional groups and increasing wettability. This increase in wettability can both favour metal sorption processes<sup>82</sup> and facilitate the release of metal-containing additives.<sup>72,80</sup>

### 3.4 Assessing the potential sources of elements in plastics

The combination of the information obtained by the analysis of total, surface extracted and sequentially extracted metals on the plastic samples helped in assessing the origin of metals in the samples; the characterization of plastic samples and the analysis of water samples gave insights into the chemical features of plastics and the water chemical conditions affecting sorption-desorption processes. The analysis of metals in the water phase further helped in investigating which metals were potentially enriched from the environment (Tables S4 and S5†).

**3.4.1 Environmental enrichment in metals.** Metals such as Fe, Al, Mn, Zn, Sr and Pb showed an (although not exclusively) enrichment likely due to metal sorption from the environment. Several of these metals (*i.e.*, Sn, Al, Mn and Pb) showed, in fact, a significantly higher extraction ratio by surface extractions in environmental samples compared to the virgin ones (Fig. 2a). This information alone, however, can also indicate that metals present as additives are more easily leached in environmental samples due to aging.<sup>67</sup>

The changes in metal fractionation between virgin and environmental samples can give further insights into understanding their origin. For example, Fe, Mn, Zn and Al exhibited a marked increase in the third extraction step, indicating a strong effect of the organic layer or the biofilm formed on plastic in the sorption of these metals from the environment. The high concentration of these elements in this step for the samples PEenv3 and PPenv2, which showed also higher absorbance in the bands representing biofilms (Fig. 4), further corroborates this hypothesis.

For Pb and Mn a significantly higher concentration was observed in environmental samples by acid digestion, too. The significantly higher total concentration further suggests an enrichment of these elements on the surface of environmental plastics in comparison with virgin samples.

Some of the abovementioned metals were also abundant in the water of Como Bay (*e.g.*, Sr: 146.39  $\mu\text{g L}^{-1}$ ; Zn: 20.90  $\mu\text{g L}^{-1}$ ; Al: 15.8  $\mu\text{g L}^{-1}$ ; Fe: 3.14  $\mu\text{g L}^{-1}$ ): this is consistent with the hypothesis of their prevailing environmental origin.

**3.4.2 Potential origin of metals as additives.** Information concerning the potential presence of metals as additives in plastics can be obtained considering the most recalcitrant fraction, especially the total digestion of plastic samples. Some of the analysed metals showed values of extraction ratios below 10% in environmental samples (*e.g.*, Cu, Ti and Ba, Fig. 2a). These elements may have mostly originated from additives within the polymeric matrix. They did not show any noticeable change between virgin and environmental samples in extraction ratios and in the total concentration after acid digestion. Cu, in addition, presented higher concentration values from sequential extraction for virgin samples than environmental ones, further confirming its presence as an additive. This element is often added to plastic polymers as a dye and biocide.<sup>88,89</sup> Ba

showed, instead, higher values for the most labile fraction in environmental samples. This is probably due to its very high concentration in an environmental sample only (PPenv2, Table S2†). Ba is in fact commonly added to plastics as a stabilizer, filler and dye (usually as barium sulphate).<sup>90</sup> Ti too did not show significant changes in the extraction ratios and in the fractionation pattern, highlighting a main source as a plastic additive. Its presence is linked to the use of TiO<sub>2</sub>, often added as a dye or UV absorber to extend polymer life and delay ageing. TiO<sub>2</sub> dispersion in the environment after plastic weathering is an already-known environmental process.<sup>39,91</sup>

Some metals with potential enrichment from the environment show low extraction ratios in environmental samples, too (*i.e.*, Zn, Al, Zn, Fe and Sr). All these metals also showed non-significant differences in the total concentration from acid digestion between environmental and virgin samples (Fig. S1†). These elements may therefore have a contribution from the plastic polymer matrix too, indicating a mixed source (*i.e.*, a contribution of both sorption from the environment and additive leaching) in environmental samples.

As a final note, the linkage between plastic colours and metal content indicated the extensive use of metal-based pigments for plastic products. For example, Pb and Ba are used as yellow pigments, while Cu, Pb and Cr-based pigments are, instead, often mixed to obtain darker variants.<sup>25,92</sup> This is evident observing the acid digestion results of our samples: the blue and green PEvir1 and PEenv2 showed a higher abundance of Fe, Zn, Cu, Ba and Cr compared to other samples (Table S1†). This is also in accordance with other reports.<sup>19,21,93</sup> In our study we also assessed an increase in the concentration of these elements in the most labile fraction (*i.e.*, step 1 of the sequential extraction). This evidence clearly shows that plastic ageing processes also make metal additives more likely to be released, and, in turn, more bioavailable.

### 3.5 Lessons learned in this study towards a refined risk assessment of metals and environmental plastics

The combination of different analytical approaches in this study helped in gaining insights into the origin of metals in environmental plastics. This approach can improve the understanding of sorption-desorption processes from the environment and help in investigating the likelihood of additive release during plastic environmental ageing. This in turn can help in improving assessment of the risk of MPs as metal vectors.<sup>37,73,94-96</sup>

The results observed from the acid digestion of plastic samples in our study (Section 3.1) showed, instead, that the total load of metals is often similar in virgin and environmental samples. This indicates a potential overestimation of the risk when exposure assessment is based upon the total acid digestion data:<sup>97,98</sup> the potential bioavailability of the metals strongly bonded within the polymer matrix relies on the kinetics of additive release, the polymer type and the grade of environmental ageing.<sup>99</sup>

The results of this study also remark on the complexity of plastic-metal interactions in the environment. Despite the



complete analytical assessment of the analysed environmental samples, the results showed high variance and several unclear trends. This indicates that plastic-metal interactions are driven by several factors at stake, such as the chemical property of the metal, polymer type, degree of ageing and the water chemical conditions. The assessment of the origin and, consequently, the potential availability of metals in plastics are therefore far from straightforward: even a thorough analytical approach as the one used in this study led to some unclear trends. Several metals (*e.g.*, Al, Fe, Sn, Sr), in fact, not surprisingly showed a possible mixed origin.

The results of this study also highlight the increase in the concentration of metals in the extractable phases in environmental samples compared to virgin ones, regardless of their origin. The processes of environmental ageing are key to affect the potential bioavailability of metals on plastic, both by increasing the sorption capacity of metals from the environment and promoting the release of additives from the polymeric matrix. Therefore, we suggest future studies to assess the potential factors changing metal bioavailability in more simplified systems (*e.g.*, micro- or mesocosms), in order to test the effects of different factors avoiding confounding factors and uncontrollable conditions (*e.g.*, adding plastics with a known amount of metal additives).

## 4. Conclusions

In this study, we examined metals associated with beached plastics sampled from Lake Como shores. We applied a multi-tiered analytical approach to differentiate the origin of metals on environmental plastic samples, possibly discerning the metals enriched by sorption processes and the additives released by plastic polymers. The analysis of the total concentration, the labile fraction and the different fractionation by extraction techniques shed light on the speciation of metals in different samples and the comparison of environmental samples and virgin plastic objects helped in assessing the background concentrations of metals in plastic polymers.

The combination of this information also helped in understanding the more likely origin of the analysed metals in the environmental samples: Mn and Pb were mostly enriched from the environment; Ba, Cu and Ti were mainly released from the polymer matrix; Zn, Sn, Sr, Fe and Al instead likely originated from a mixed source.

This study also showed that environmental samples generally present higher concentrations of labile metals, which indicates a potential increased environmental risk of metal bonded to plastics induced by polymer ageing processes. The sequential extraction results also indicated an increase of several metals (*e.g.*, Al, Fe, Zn) in the organic matter bonded fraction, confirming the important role of organic matter and biofilms in mediating the sorption process of metals from the environment. Overall, our findings highlighted the role of plastics as potential carriers for the transfer of metals in freshwater media and confirmed that field studies can give important insights into the environmental risk related to this issue.

## Author contributions

Conceptualization: SC and GB (Gilberto Binda); methodology: SC, DS, DM, and GB (Gilberto Binda); investigation: SC, DS, and GB (Ginevra Boldrocchi); data curation: SC, AP, and RB; writing (original draft): SC; writing (review and editing): AP, DS, DM, RB, GB (Ginevra Boldrocchi), LN, and GB (Gilberto Binda); supervision: AP, RB, and LN; funding acquisition: LN and GB (Gilberto Binda).

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was funded by the European Commission under the H2020 MSCA-IF project “PLANET-understanding PLASTic pollution effects on the biogeochemical cycle of Elements” (grant number 101023603). The authors would also acknowledge the three anonymous reviewers for their helpful comments and suggestions.

## Notes and references

- 1 A. L. Andrady, *Mar. Pollut. Bull.*, 2011, **62**, 1596–1605.
- 2 S. Liu, J. Huang, W. Zhang, L. Shi, K. Yi, H. Yu, C. Zhang, S. Li and J. Li, *J. Environ. Manage.*, 2022, **302**, 113995.
- 3 C. M. Rochman, M. A. Browne, B. S. Halpern, B. T. Hentschel, E. Hoh, H. K. Karapanagioti, L. M. Rios-Mendoza, H. Takada, S. Teh and R. C. Thompson, *Nature*, 2013, **494**, 169–171.
- 4 T. Zhang, B. Jiang, Y. Xing, H. Ya, M. Lv and X. Wang, *Environ. Sci. Pollut. Res.*, 2022, **29**, 16830–16859.
- 5 W. Steffen, Å. Persson, L. Deutsch, J. Zalasiewicz, M. Williams, K. Richardson, C. Crumley, P. Crutzen, C. Folke, L. Gordon, M. Molina, V. Ramanathan, J. Rockström, M. Scheffer, H. J. Schellnhuber and U. Svedin, *Ambio*, 2011, **40**, 739–761.
- 6 J. Zalasiewicz, C. N. Waters, J. A. Ivar do Sul, P. L. Corcoran, A. D. Barnosky, A. Cearreta, M. Edgeworth, A. Gałuszka, C. Jeandel, R. Leinfelder, J. R. McNeill, W. Steffen, C. Summerhayes, M. Wagemann, M. Williams, A. P. Wolfe and Y. Yonah, *Anthropocene*, 2016, **13**, 4–17.
- 7 *Plastic Debris in the Ocean: The Characterization of Marine Plastics and Their Environmental Impacts, Situation Analysis Report*, ed. F. Thevenon, C. Carroll and J. Sousa, International Union for Conservation of Nature, 2015.
- 8 D. Fu, Q. Zhang, Z. Fan, H. Qi, Z. Wang and L. Peng, *Aquat. Toxicol.*, 2019, **216**, 105319.
- 9 X. Guo and J. Wang, *Mar. Pollut. Bull.*, 2019, **142**, 1–14.
- 10 J. Zou, X. Liu, D. Zhang and X. Yuan, *Chemosphere*, 2020, **248**, 126064.
- 11 G. Kutralam-Muniasamy, F. Pérez-Guevara, I. Elizalde-Martínez and V. C. Shruti, *Sci. Total Environ.*, 2020, **714**, 136823.
- 12 D. Peixoto, C. Pinheiro, J. Amorim, L. Oliva-Teles, L. Guilhermino and M. N. Vieira, *Estuarine, Coastal Shelf Sci.*, 2019, **219**, 161–168.



- 13 V. C. Shruti, F. Pérez-Guevara, I. Elizalde-Martínez and G. Kutralam-Muniasamy, *Sci. Total Environ.*, 2020, **726**, 138580.
- 14 G. Chen, Q. Fu, X. Tan, H. Yang, Y. Luo, M. Shen and Y. Gu, *Environ. Pollut.*, 2022, **295**, 118695.
- 15 A. P. da Costa Araújo, N. F. S. de Melo, A. G. de Oliveira Junior, F. P. Rodrigues, T. Fernandes, J. E. de Andrade Vieira, T. L. Rocha and G. Malafaia, *J. Hazard. Mater.*, 2020, **382**, 121066.
- 16 J.-P. W. Desforges, M. Galbraith and P. S. Ross, *Arch. Environ. Contam. Toxicol.*, 2015, **69**, 320–330.
- 17 M. Long, B. Moriceau, M. Gallinari, C. Lambert, A. Huvet, J. Raffray and P. Soudant, *Mar. Chem.*, 2015, **175**, 39–46.
- 18 X. Li, Y. Chen, S. Zhang, Y. Dong, Q. Pang, I. Lynch, C. Xie, Z. Guo and P. Zhang, *Ecotoxicol. Environ. Saf.*, 2023, **251**, 114564.
- 19 K. Ashton, L. Holmes and A. Turner, *Mar. Pollut. Bull.*, 2010, **60**, 2050–2055.
- 20 L. A. Holmes, A. Turner and R. C. Thompson, *Environ. Pollut.*, 2012, **160**, 42–48.
- 21 A. Turner and L. A. Holmes, *Environ. Chem.*, 2015, **12**, 600.
- 22 Y. Dong, M. Gao, Z. Song and W. Qiu, *Environ. Pollut.*, 2019, **254**, 112950.
- 23 P. Liu, K. Lu, J. Li, X. Wu, L. Qian, M. Wang and S. Gao, *J. Hazard. Mater.*, 2020, **384**, 121193.
- 24 V. Ambrogi, C. Carfagna, P. Cerruti and V. Marturano, in *Modification of Polymer Properties*, ed. C. F. Jasso-Gastinel and J. M. Kenny, William Andrew Publishing, 2017, pp. 87–108.
- 25 C. Catrouillet, M. Davranche, I. Khatib, C. Fauny, A. Wahl and J. Gigault, *Environ. Sci.: Processes Impacts*, 2021, **23**, 553–558.
- 26 J. N. Hahladakis, C. A. Velis, R. Weber, E. Iacovidou and P. Purnell, *J. Hazard. Mater.*, 2018, **344**, 179–199.
- 27 F. Gao, J. Li, C. Sun, L. Zhang, F. Jiang, W. Cao and L. Zheng, *Mar. Pollut. Bull.*, 2019, **144**, 61–67.
- 28 J. P. Rodrigues, A. C. Duarte and J. Santos-Echeandía, *J. Hazard. Mater. Adv.*, 2022, **6**, 100072.
- 29 G. Chen, Q. Fu, X. Tan, H. Yang, Y. Luo, M. Shen and Y. Gu, *Environ. Pollut.*, 2022, **295**, 118695.
- 30 G. Kalčíková, T. Skalar, G. Marolt and A. Jemec Kokalj, *Water Res.*, 2020, **175**, 115644.
- 31 M. Salehi, C. T. Jafvert, J. A. Howarter and A. J. Whelton, *J. Hazard. Mater.*, 2018, **347**, 242–251.
- 32 J. Meng, B. Xu, F. Liu, W. Li, N. Sy, X. Zhou and B. Yan, *Chemosphere*, 2021, **283**, 131274.
- 33 G. Binda, G. Zanetti, A. Bellasi, D. Spanu, G. Boldrocchi, R. Bettinetti, A. Pozzi and L. Nizzetto, *Environ. Sci. Pollut. Res.*, 2023, **30**, 6298–6312.
- 34 M. Ahechti, M. Benomar, M. El Alami and C. Mendiguchía, *Int. J. Environ. Anal. Chem.*, 2022, **102**, 1118–1125.
- 35 G. Binda, D. Spanu, D. Monticelli, A. Pozzi, A. Bellasi, R. Bettinetti, S. Carnati and L. Nizzetto, *Water Res.*, 2021, **204**, 117637.
- 36 V. Godoy, G. Blázquez, M. Calero, L. Quesada and M. A. Martín-Lara, *Environ. Pollut.*, 2019, **255**, 113363.
- 37 L. A. Holmes, A. Turner and R. C. Thompson, *Mar. Chem.*, 2014, **167**, 25–32.
- 38 Y. Cao, M. Zhao, X. Ma, Y. Song, S. Zuo, H. Li and W. Deng, *Sci. Total Environ.*, 2021, **788**, 147620.
- 39 C. Campanale, I. Savino, C. Massarelli and V. F. Uricchio, *NanoImpact*, 2022, **28**, 100438.
- 40 C. Catrouillet, M. Davranche, I. Khatib, C. Fauny, A. Wahl and J. Gigault, *Environ. Sci.: Processes Impacts*, 2021, **23**, 553–558.
- 41 I. Savino, C. Campanale, P. Trotti, C. Massarelli, G. Corriero and V. F. Uricchio, *Polymers*, 2022, **14**, 1958.
- 42 M. E. Hodson, C. A. Duffus-Hodson, A. Clark, M. T. Prendergast-Miller and K. L. Thorpe, *Environ. Sci. Technol.*, 2017, **51**, 4714–4721.
- 43 L. A. Holmes, R. C. Thompson and A. Turner, *Environ. Pollut.*, 2020, **261**, 114107.
- 44 G. Kutralam-Muniasamy, F. Pérez-Guevara, I. E. Martínez and V. C. Shruti, *J. Hazard. Mater.*, 2021, **415**, 125755.
- 45 A. Turner, *Environ. Pollut.*, 2018, **236**, 1020–1026.
- 46 G. Binda, S. Carnati, D. Spanu, A. Bellasi, R. Hurley, R. Bettinetti, D. Monticelli, A. Pozzi and L. Nizzetto, *J. Hazard. Mater.*, 2023, **452**, 131330.
- 47 W. Li, H.-S. Lo, H.-M. Wong, M. Zhou, C.-Y. Wong, N. F.-Y. Tam and S.-G. Cheung, *Mar. Pollut. Bull.*, 2020, **153**, 110977.
- 48 A. T. Ta and S. Babel, *Chemosphere*, 2020, **257**, 127234.
- 49 J. Wang, J. Peng, Z. Tan, Y. Gao, Z. Zhan, Q. Chen and L. Cai, *Chemosphere*, 2017, **171**, 248–258.
- 50 A. Bellasi, G. Binda, A. Pozzi, S. Galafassi, P. Volta and R. Bettinetti, *Environments*, 2020, **7**, 30.
- 51 R. Leiser, G.-M. Wu, T. R. Neu and K. Wendt-Potthoff, *Water Res.*, 2020, **176**, 115748.
- 52 D. Copetti, N. Guyennon and F. Buzzi, *Sci. Total Environ.*, 2020, **749**, 141587.
- 53 W. Scheffler and G. Morabito, *J. Limnol.*, 2003, **62**, 47–60.
- 54 G. Binda, F. Frascoli, D. Spanu, M. F. Ferrario, S. Terrana, R. Gambillara, S. Trotta, P. J. Noble, F. A. Livio, A. Pozzi and A. M. Michetti, *Water*, 2022, **14**, 124.
- 55 A. Bellasi, G. Binda, G. Boldrocchi, A. Pozzi and R. Bettinetti, *Appl. Sci.*, 2022, **12**, 5388.
- 56 K. I. Martínez, R. González-Mota, J. J. Soto-Bernal and I. Rosales-Candelas, *J. Appl. Polym. Sci.*, 2021, **138**, 50158.
- 57 A. Jansson, K. Möller and T. Gevert, *Polym. Degrad. Stab.*, 2003, **82**, 37–46.
- 58 X. Bai, F. Li, L. Ma and C. Li, *Sci. Total Environ.*, 2022, **804**, 150168.
- 59 W. Han, J. Shin and J. Ho Shin, *HardwareX*, 2022, **12**, e00327.
- 60 L. Hildebrandt, M. von der Au, T. Zimmermann, A. Reese, J. Ludwig and D. Pröfrock, *PLoS ONE*, 2020, **15**, 1–18.
- 61 M. Pueyo, J. F. López-Sánchez and G. Rauret, *Anal. Chim. Acta*, 2004, **504**, 217–226.
- 62 G. Binda, A. Pozzi, F. Livio, P. Piasini and C. Zhang, *J. Geochem. Explor.*, 2018, **190**, 58–68.
- 63 M. R. Rosen, G. Binda, C. Archer, A. Pozzi, A. M. Michetti and P. J. Noble, *Water Resour. Res.*, 2018, **54**, 5225–5244.
- 64 D. Monticelli, A. Castelletti, D. Civati, S. Recchia and C. Dossi, *Int. J. Anal. Chem.*, 2019, **2019**, 1–5.



- 65 R. A. Hites, *Environ. Sci. Technol.*, 2019, **53**, 11059–11060.
- 66 A. Bellasi, G. Binda, A. Pozzi, G. Boldrocchi and R. Bettinetti, *Chemosphere*, 2021, **278**, 130357.
- 67 W. Feng, C. Huang, X. Tan, N. Tang, L. Zhang, H. Li, X. Xu and J. Peng, *Ecotoxicology*, 2022, **31**, 75–84.
- 68 S. He, M. Jia, Y. Xiang, B. Song, W. Xiong, J. Cao, H. Peng, Y. Yang, W. Wang, Z. Yang and G. Zeng, *J. Hazard. Mater.*, 2022, **424**, 127286.
- 69 W. Qiongjie, Z. Yong, Z. Yangyang, L. Zhouqi, W. Jinxiaoxue and C. Huijuan, *J. Hazard. Mater.*, 2022, **424**, 127340.
- 70 H. Richard, E. J. Carpenter, T. Komada, P. T. Palmer and C. M. Rochman, *Sci. Total Environ.*, 2019, **683**, 600–608.
- 71 M. Horváth, G. Halász, E. Kucanová, B. Kuciková, I. Fekete, D. Remeteiová, G. Heltai and K. Flórián, *Microchem. J.*, 2013, **107**, 121–125.
- 72 Q. Fu, X. Tan, S. Ye, L. Ma, Y. Gu, P. Zhang, Q. Chen, Y. Yang and Y. Tang, *Chemosphere*, 2021, **270**, 128624.
- 73 L. Gao, D. Fu, J. Zhao, W. Wu, Z. Wang, Y. Su and L. Peng, *Mar. Pollut. Bull.*, 2021, **169**, 112480.
- 74 L. Wang, C. Guo, Q. Qian, D. Lang, R. Wu, S. Abliz, W. Wang and J. Wang, *Chemosphere*, 2023, **313**, 137439.
- 75 Q. Wang, Y. Zhang, X. Wangjin, Y. Wang, G. Meng and Y. Chen, *J. Environ. Sci.*, 2020, **87**, 272–280.
- 76 Y. Xia, S. Niu, T. Wang and J. Wu, *Mar. Pollut. Bull.*, 2023, **187**, 114588.
- 77 Y.-B. Ma, Z.-Y. Xie, N. Hamid, Q.-P. Tang, J.-Y. Deng, L. Luo and D.-S. Pei, *Aquat. Toxicol.*, 2023, **261**, 106597.
- 78 M. R. Jung, F. D. Horgen, S. V. Orski, V. Rodriguez C., K. L. Beers, G. H. Balazs, T. T. Jones, T. M. Work, K. C. Brignac, S.-J. Royer, K. D. Hyrenbach, B. A. Jensen and J. M. Lynch, *Mar. Pollut. Bull.*, 2018, **127**, 704–716.
- 79 S. Tang, L. Lin, X. Wang, A. Feng and A. Yu, *J. Hazard. Mater.*, 2020, **386**, 121960.
- 80 K. Aghilinasrollahabadi, M. Salehi and T. Fujiwara, *J. Hazard. Mater.*, 2021, **408**, 124439.
- 81 M. M. Rahman, S. Al-Sulaimi and A. M. Farooque, *Appl. Water Sci.*, 2018, **8**, 183.
- 82 G. Binda, M. Costa, L. Supraha, D. Spanu, C. Vogelsang, E. Leu and L. Nizzetto, *Sci. Total Environ.*, 2023, **893**, 164807.
- 83 K. Qi, N. Lu, S. Zhang, W. Wang, Z. Wang and J. Guan, *J. Hazard. Mater.*, 2021, **411**, 125115.
- 84 Q. Xie, H. Li, Z. Li, H. Zhang, M. Yuan, M. Wu, H. Li and X. Xu, *Gondwana Res.*, 2022, **108**, 181–192.
- 85 G. Peng, Z. Pu, F. Chen, H. Xu, X. Cao, C. Chun Chen, J. Wang, Y. Liao, X. Zhu and K. Pan, *Environ. Int.*, 2023, **177**, 107988.
- 86 R. Mao, M. Lang, X. Yu, R. Wu, X. Yang and X. Guo, *J. Hazard. Mater.*, 2020, **393**, 122515.
- 87 M. S. Dodhia, K. L. Rogers, V. Fernández-Juárez, J. A. Carreres-Calabuig, C. R. Löscher, A. A. Tisserand, N. Keulen, L. Riemann, Y. Shashoua and N. R. Posth, *Front. Mar. Sci.*, 2023, **10**, 1134815.
- 88 H. K. Imhof, C. Laforsch, A. C. Wiesheu, J. Schmid, P. M. Anger, R. Niessner and N. P. Ivleva, *Water Res.*, 2016, **98**, 64–74.
- 89 C. Arcos, L. Muñoz, D. Cordova, H. Muñoz, M. Walter, M. I. Azócar, Á. Leiva, M. Sancy and G. Rodríguez-Grau, *Polymers*, 2022, **14**, 5220.
- 90 A. Turner and M. Filella, *Mar. Pollut. Bull.*, 2020, **158**, 111352.
- 91 H. Luo, Y. Xiang, Y. Li, Y. Zhao and X. Pan, *Sci. Total Environ.*, 2020, **729**, 139083.
- 92 H. El Hadri, J. Gigault, S. Mounicou, B. Grassl and S. Reynaud, *Mar. Pollut. Bull.*, 2020, **160**, 111716.
- 93 S. Dobaradaran, T. C. Schmidt, I. Nabipour, N. Khajeahmadi, S. Tajbakhsh, R. Saeedi, M. Javad Mohammadi, M. Keshtkar, M. Khorsand and F. Faraji Ghasemi, *Waste Manage.*, 2018, **78**, 649–658.
- 94 D. Brennecke, B. Duarte, F. Paiva, I. Caçador and J. Canning-Clode, *Estuarine, Coastal Shelf Sci.*, 2016, **178**, 189–195.
- 95 M. Kedzierski, M. D'Almeida, A. Magueresse, A. Le Grand, H. Duval, G. César, O. Sire, S. Bruzaud and V. Le Tilly, *Mar. Pollut. Bull.*, 2018, **127**, 684–694.
- 96 C. Campanale, C. Massarelli, I. Savino, V. Locaputo and V. F. Uricchio, *Int. J. Environ. Res. Public Health*, 2020, **17**, 1212.
- 97 P. Klöckner, T. Reemtsma and S. Wagner, *Sci. Total Environ.*, 2021, **764**, 142870.
- 98 A. Turner and M. Filella, *Environ. Int.*, 2021, **156**, 106622.
- 99 A. Turner, L. Holmes, R. C. Thompson and A. S. Fisher, *Water Res.*, 2020, **173**, 115577.

