



CrystEngComm

**Application of a tetrapyrimidyl cyclobutane synthesized in the organic solid state: a halogen-bonded supramolecular ladder**

Journal:	<i>CrystEngComm</i>
Manuscript ID	CE-COM-09-2020-001280.R1
Article Type:	Communication
Date Submitted by the Author:	26-Sep-2020
Complete List of Authors:	Sinnwell, Michael; Pacific Northwest National Laboratory, Physical and Computational Sciences Directorate Santana, Carlos; Webster University Bosch, Eric; Missouri State University, Chemistry MacGillivray, Len; University of Iowa, Department of Chemistry Groeneman, Ryan; Webster University, Biological Sciences

SCHOLARONE™  
Manuscripts



Journal Name

COMMUNICATION

## Application of a tetrapyrimidyl cyclobutane synthesized in the organic solid state: a halogen-bonded supramolecular ladder

Received 00th January 20xx,  
Accepted 00th January 20xx

Michael A. Sinnwell,<sup>a</sup> Carlos L. Santana,<sup>b</sup> Eric Bosch,<sup>c</sup> Leonard R. MacGillivray\*<sup>a</sup> and Ryan H. Groeneman\*<sup>b</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org


**A halogen-bonded supramolecular ladder comprised of a novel pyrimidine-based cyclobutane photoproduct synthesized in the organic solid state via a [2 + 2] photoreaction is reported. The photoproduct *rctt*-tetrakis(5'-pyrimidyl)cyclobutane functions as rungs while the linear divergent halogen-bond donor 1,4-diiodoperchlorobenzene acts as the rails. Our report also confirms the structure and stereochemistry of the tetrapyrimidyl cyclobutane ring system.**

The formation of organic networks continues to be an active area of research for materials scientists and crystal engineers. Diversifying the geometry of molecular nodes and linkers continues to afford network solids of varied topologies.<sup>1</sup> An approach that can instil diversity into these solids is based upon the modularity of the components. Recently, the ability of tetrafunctional *rctt*-tetrakis(4-pyridyl)cyclobutane, a photoproduct generated in the organic solid state, to form both a square lattice<sup>2</sup> and a diamondoid net<sup>3</sup> has been reported by the simple variation of the halogen-bond donor. In particular, the square lattice was realized when the cyclobutane is combined with 1,4-diiodoperfluorobenzene while the isosteric donor 1,4-diiodoperchlorobenzene ( $C_6I_2Cl_4$ ) yielded a diamondoid net.

Cyclobutane-based products generated in the solid state are ideal building blocks to investigate modularity of these networks within organic solids. Since, the pendant groups attached to the cyclobutane ring system can be modified based on substituents attached to the central carbon-carbon double (C=C) bond before photoreaction.<sup>4</sup> To date, all cyclobutane-based molecules synthesized in the solid state that have been used deliberately as building blocks to form

extended organic networks have possessed *n*-pyridyl substituents as linker groups.<sup>5</sup> It stands to reason that extending the solid-state reactivity to cyclobutane rings lined with other heterocycles could significantly expand the scope of using this chemistry for network design and discovery.

Here, we report the application of the tetrafunctional photoproduct *rctt*-tetrakis(5'-pyrimidyl)cyclobutane (**TPmCB**) as a molecular building block that supports a halogen-bonded supramolecular ladder (Scheme 1). One of us has reported that *trans*-1,2-bis(5'-pyrimidyl)ethylene (**BPmE**) is photoactive and undergoes a [2 + 2] cycloaddition reaction in the solid state as a pure solid to yield a cyclobutane product.<sup>6</sup> The product is, thus, generated without assistance of auxiliary molecules (e.g. ditopic templates) and reacts quantitatively and without side products. The stereochemistry of the photoproduct remained, however, unassigned yet based on the structure of crystalline **BPmE** would be expected as **TPmCB**. In addition to now confirming the stereochemistry of the novel tetra(pyrimidyl)cyclobutane photoproduct, we also show that co-crystallization of **TPmCB** with the exo-divergent halogen-bond donor  $C_6I_2Cl_4$  results in a supramolecular ladder wherein **TPmCB** and  $C_6I_2Cl_4$  act as the rungs and rails, respectively. While supramolecular ladders have been formed using hydrogen bonds and coordination chemistry, there are only a

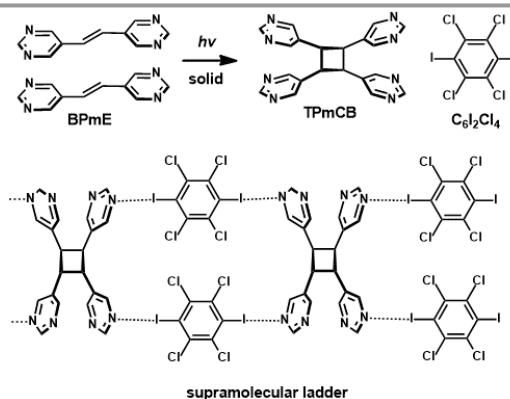

**Scheme 1.** [2 + 2] cycloaddition reaction to form **TPmCB** in the organic solid state and the resulting supramolecular ladder held together by halogen bonds from  $C_6I_2Cl_4$ .

<sup>a</sup> Department of Chemistry, University of Iowa, Iowa City, IA 65804, USA. Email: len-macgillivray@uiowa.edu, Tel: +1 319-335-3504.

<sup>b</sup> Department of Biological Sciences, Webster University, St. Louis, MO 63119, USA. Email: ryangroeneman19@webster.edu, Tel: +1 314-246-7466.


<sup>c</sup> Department of Chemistry, Missouri State University, Springfield, MO 65804, USA.

† Electronic Supplementary Information (ESI) available: experimental details, single crystal X-ray data, and <sup>1</sup>H NMR spectra. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/x0xx00000x.

limited number of supramolecular ladders sustained by halogen bonds.<sup>7</sup> To the best of our knowledge, this is the first reported co-crystal based upon a tetrafunctional photoproduct based upon the pyrimidyl ring system. Our work, thus, expands the diversity of photoproducts generated by the solid-state synthesis approach. The ladder reported here hosts toluene molecules in the form of (TPmCB)•2(C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>)•(toluene) (**1**).

The components of the ladder of **1** are not commercially available and were synthesized as reported.<sup>6,8</sup> The tetra(pyrimidyl)photoproduct was generated in near quantitative yield by exposing UV light (medium-pressure Hg lamp) to a powdered sample of BPmE in a period of 20 hours (Fig S1). The solid was used directly following the photoreaction. Single crystals of TPmCB (25.0 mg) in the form of plates suitable for single-crystal X-ray diffraction were generated by dissolution and slow evaporation from ethanol (3.0 mL).

The cyclobutane crystallizes in the monoclinic space group C2/c. The asymmetric unit contains one half of a molecule of TPmCB that sits on a centre of inversion. The stereochemistry of the cyclobutane is confirmed as the *rctt*-isomer (Figure 1a). In the arrangement, TPmCB, which is disordered over two sites (site occupancies: 0.89 and 0.11), is sustained *via* face-to-face  $\pi$ - $\pi$  stacking (3.67 Å) and C-H...N hydrogen bonds [C...N 3.662(4) Å; C-H...N 160.57(16)°] of the pendant pyrimidyl rings (Figures 1b and 1c).

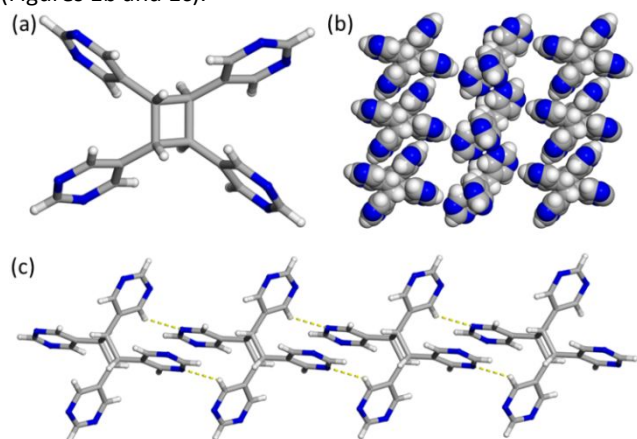


**Figure 1.** X-ray crystal structure TPmCB: (a) view of *rctt* stereochemistry of the cyclobutane ring, (b) face-to-face  $\pi$ - $\pi$  stacking of the pyrimidyl rings, and (c) C-H...N hydrogen bonds of the extended solid (yellow dashes = hydrogen bonds). The disorder in TPmCB was removed for clarity.

A supramolecular ladder forms when TPmCB is co-crystallized with C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>. Single crystals of **1** in the form of blocks were realized upon slow evaporation by combining an ethanol (2.0 mL) and toluene (1.0 mL) solution of TPmCB (25.0 mg) and a warm toluene (2.0 mL) solution of C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub> (63.5 mg) (1:2 molar ratio).


The components of **1** crystallize in the triclinic space group P $\bar{1}$ . The asymmetric unit contains one half of a molecule of TPmCB, one molecule of C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>, and a disordered toluene molecule that resides on a centre of inversion. Each pyrimidyl ring participates in a single I...N halogen bond with C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>

[I...N 2.865(2) and 2.991(2) Å; C-I...N 177.44(8) and 165.49(9)°] to afford a supramolecular ladder (Figure 2a).<sup>9</sup> TPmCB, thus, acts as a 4-connected node that serves as the rungs while C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub> serves as the rails. In addition, TPmCB acts as an H-shaped building block to form the ladder.<sup>10</sup>

The formation of the supramolecular ladder does not require each N-atom of TPmCB to participate in a halogen bond. Moreover, two of the remaining N-atoms are engaged in a C-H...N interactions [C...N 3.467(7) Å; C-H...N 155.4(5)°] with the *ortho*-hydrogen on the included toluene. The interaction results in the formation of a two-dimensional sheet (Figure 2b). Thus, each cyclobutane is engaged in four I...N halogen bonds and two C-H...N hydrogen bonds. The sheets stack with the included toluene molecules sandwiched between nearest-neighbouring cyclobutane rings. The four-membered ring participates in C-H... $\pi$  interactions with the aromatic solvent (Figure 3a). The interactions are manifested as infinite columns running along the crystallographic *a*-axis (Figure 3b).

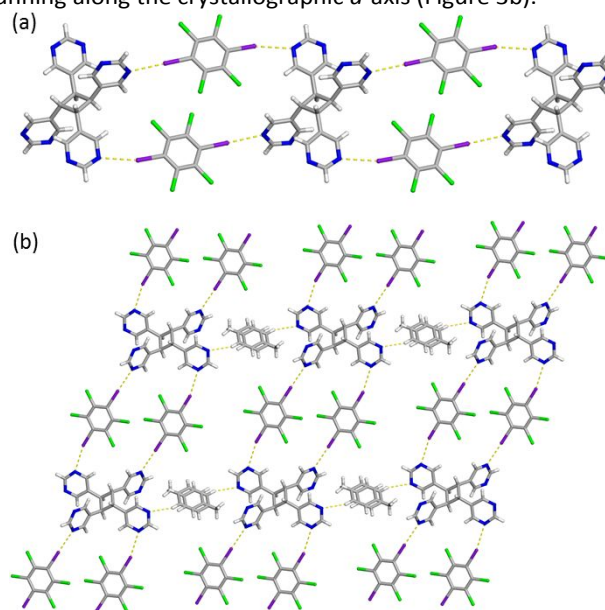

**Figure 2.** X-ray structure of **1**: (a) illustrating the supramolecular ladder and (b) the two-dimensional sheets of **1** (yellow dashes = halogen and hydrogen bonds).

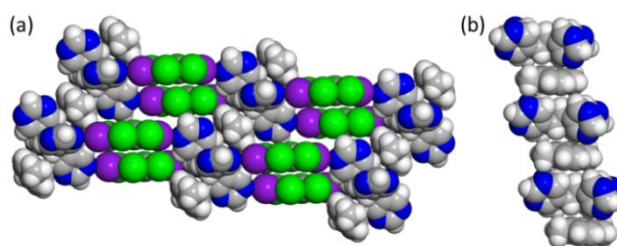

**Figure 3.** X-ray structure of **1**: (a) illustrating C-H... $\pi$  interaction between TPmCB and the included toluene molecule and (b) a closer view of the infinite stacking of the components.

## Conclusions

We have utilized the solid state to generate a cyclobutane-based building block in the form of **TPmCB** that yields a supramolecular ladder when co-crystallized with **C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>**. The components self-assemble via halogen bonds with the photoproduct acting as H-shaped nodes of the ladder. Overall, the **TPmCB** acts as the rungs while **C<sub>6</sub>I<sub>2</sub>Cl<sub>4</sub>** acts as the rails. Currently, we are attempting to incorporate **TPmCB** into other organic solids, as well as metal-organic materials, and expand the inclusion properties of this emerging class of pyrimidyl-based solids.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

R. H. G. gratefully acknowledges financial support from Webster University in the form of various Faculty Research Grants. L. R. M. acknowledges support from the National Science Foundation (DMR-1708673). Lastly, funding from the National Science Foundation (CHE-1827756) for the purchase of the Bruker Venture Duo Photon-II diffractometer is also acknowledged.


## Notes and references

- (a) S. M. Oburn, M. A. Sinnwell, D. P. Ericson, E. W. Reinheimer, D. M. Proserpio, R. H. Groeneman and L. MacGillivray, *IUCrJ*, 2019, **6**, 1032; (b) I. Hisaki, C. Xin, K. Takahashi and T. Nakamura, *Angew. Chem. Int. Ed.*, 2019, **58**, 11160; (c) V. Kumar, T. Pilati, G. Terraneo, F. Meyer, P. Metrangolo and G. Resnati, *Chem. Sci.*, 2017, **8**, 1801; (d) T. Adachi and M. D. Ward, *Acc. Chem. Res.*, 2016, **49**, 2669.
- M. Baldrighi, P. Metrangolo, F. Meyer, T. Pilati, D. Proserpio, G. Resnati and G. Terraneo, *J. Fluor. Chem.*, 2010, **131**, 1218.
- S. M. Oburn, C. L. Santana, E. Elacqua and R. H. Groeneman, *CrystEngComm*, 2020, **22**, 4349.
- (a) M.-M. Gan, J.-G. Yu, Y.-Y. Wang and Y.-F. Han, *Cryst. Growth Des.*, 2018, **18**, 553; (b) V. Ramamurthy and J. Sivaguru, *Chem. Rev.*, 2016, **116**, 9914; (c) K. Biradha and R. Santra, *Chem. Soc. Rev.*, 2013, **42**, 950.
- For an extended network that forms from a SCSC reaction that contain a carboxylic acid see: S. Bhattacharya, J. Stojaković, B. K. Saha, and L. R. MacGillivray, *Org. Lett.* 2013, **15**, 744.
- E. Bosch, J. M. Matheny and N. P. Rath, *Synth. Commun.*, 2007, **37**, 3835.
- (a) J. Quentin, D. C. Swenson and L. R. MacGillivray, *Molecules*, 2020, **25**, 907; (b) M. A. Sinnwell, J. N. Blad, L. R. Thomas and L. R. MacGillivray, *IUCrJ*, 2018, **5**, 491; (c) T. Caronna, R. Liantonio, T. A. Logothetis, P. Metrangolo, T. Pilati and G. Resnati, *J. Am. Chem. Soc.*, 2004, **126**, 4500.
- C. M. Reddy, M. T. Kirchner, R. C. Gundakaram, K. A. Padmanabhan and G. R. Desiraju, *Chem. Eur.*, 2006, **12**, 2222.
- (a) C. I. Nwachukwu, L. J. Patton, N. P. Bowling and E. Bosch, *Acta Cryst.*, 2020, **C76**, 458; (b) A. E. S. Hardin, T. L. Ellington, S. T. Nguyen, A. L. Rheingold, G. S. Tschumper, D. L. Watkins and N. I. Hammer, *Inorganics*, 2019, **7**, 119; (c) T. L. Ellington, P. L. Reves, B. L. Simms, J. L. Wilson, D. L. Watkins, G. S.

Tschumper and N. I. Hammer, *ChemPhysChem*, 2017, **18**, 1267.

- A. N. Sokolov and L. R. MacGillivray, *Cryst. Growth Des.*, 2006, **6**, 2615.

## For Table of Contents Use Only

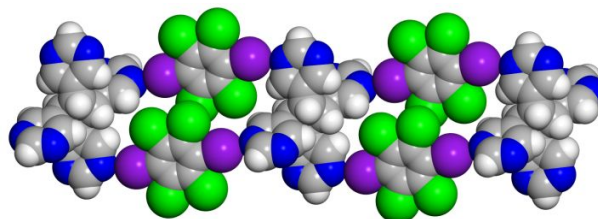

A supramolecular ladder sustained by halogen bonds with rungs based upon a photoproduct, namely *rctt*-tetrakis(5'-pyrimidyl)cyclobutane, generated in the solid state is reported.