



Cite this: *J. Mater. Chem. A*, 2016, **4**, 6933

## A rechargeable self-healing safety fuel gel†

Santu Bera and Debasish Haldar\*

The stimuli responsive assembly of small molecules that can modulate the physical properties of a supramolecular system may have potential as futuristic materials. The dimethyl dipicolinate in alcohol, when combined with 3 equiv. of potassium hydroxide and water, aggregates to a strong self-healing transparent gel. The instant gelation is highly selective towards potassium hydroxide and does not need any heating–cooling or sonication. The gelation is also selective for solvent systems such as 9 : 1 methanol–water or ethanol–water. The rheological stepstrain measurements under varying strain at room temperature show that the gel is thixotropic in nature. The gel can be shaped like any free-standing objects due to its high mechanical strength. The gel exhibits remarkable self-healing properties when damaged and diffusion of methyl orange through the gel suggests the dynamic nature of the gel. We found that the non-explosive gel can be packaged in a polyethylene tube and used as a safe fuel for indoor and outdoor heating without any special stove or burner. The gelator retains strong memory even after burning which makes it rechargeable up to four times by the addition of (9 : 1) methanol–water.

Received 6th October 2015  
Accepted 9th November 2015

DOI: 10.1039/c5ta08010j

[www.rsc.org/MaterialsA](http://www.rsc.org/MaterialsA)

## 1. Introduction

Molecular recognition and self-assembly processes are key for developing new functional materials such as supramolecular gels.<sup>1–9</sup> Generally supramolecular gels are entangled networks of

fibers composed of self-assembled building blocks that can entrap relatively large amounts of solvents.<sup>10–12</sup> Due to the reversibility of the formation through noncovalent interactions and their degradability, homogeneity, and tunability<sup>13</sup> the supramolecular gels have excellent responsiveness to different stimuli, such as pH, light, enzyme, ions, temperature, ultrasound and mechanical strength.<sup>14</sup> The supramolecular gels have potential applications including sensing of biomolecules and ions, light-harvesting systems,<sup>15–19</sup> catalysis,<sup>20</sup> optoelectronic devices,<sup>21</sup> and as media for cell culture, tissue engineering and targeted drug delivery.<sup>22–29</sup> Many organic motifs such as steroids,<sup>30</sup> peptides,<sup>31–34</sup> ureas and amides,<sup>35–40</sup> sugars,<sup>41</sup> dendrimers,<sup>42,43</sup> and  $\pi$ -conjugated molecules<sup>44,45</sup> have been designed and developed as gelatos. But, most of these organic gelator molecules need to be synthesized by tedious procedures. Exploration of simple and effective gelator molecules with novel functions is highly challenging.<sup>46–48</sup>

Historically alcohols are known as fuel. Methanol and ethanol can be obtained from fossil fuels and biomass or industrially from  $\text{CO}_2$  and water. They have high octane rating and advantages over fuels such as petrol and diesel. As an alternative of hydrogen, methanol has been proposed as a future green fuel. However, their liquid nature and relatively high volatility make them inconvenient to use for different purposes. There are also issues with spilling and safety. Hence, converting liquid alcohols into gel will be highly advantageous for easy handling, delivery and safety.

Herein we report one stimuli responsive simple gelator that can congeal an alcohol–water mixture to give a strong, self-supporting, and transparent gel with magnificent self-healing properties. The gelation is highly selective for potassium hydroxide. Interestingly, the assembly of gelator molecules can

Department of Chemical Sciences, Indian Institute of Science Education and Research Kolkata, Mohanpur 741252, West Bengal, India. E-mail: [deba\\_h76@yahoo.com](mailto:deba_h76@yahoo.com); [deba\\_h76@iiserkol.ac.in](mailto:deba_h76@iiserkol.ac.in); Fax: +91 3325873020; Tel: +91 3325873119

† Electronic supplementary information (ESI) available: Synthesis and characterization of compound 1,  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR, Fig. ESI S1–S14, and Fig. S1–S6. CCDC 918260. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5ta08010j



Debasish Haldar is an Associate Professor in the Department of Chemical Sciences, Indian Institute of Science, Education and Research, Kolkata, India. He has studied chemistry at the University of Calcutta and obtained his PhD in organic chemistry from IACS/Jadavpur University, India in 2005. After post-doctoral studies at the IECB in France, the University of Manchester in U.K. and the University of Würzburg in

Germany he joined the IISER-Kolkata in 2008 as Assistant Professor. He has research experience and interests ranging across the synthesis of amino acids and analogues, peptides and peptidomimetics and their structures and functions.



effectively trap methanol or ethanol in the presence of water (9 : 1). The gel exhibits high stability, thixotropic behaviour and self-healing properties. We also demonstrate novel applications of this gel as a safe fuel for indoor and outdoor heating without any special stove or burner. The gelator retains strong memory even after burning which makes it reusable up to four times by the addition of (9 : 1) methanol/water. The eco-friendly gel can be coloured with organic dyes and can be packed in any container.

## 2. Results and discussion

For instant gelation, we chose a non-covalent approach. The greener part is that the gelation does not need any heating-cooling cycle or sonication. The gel consists of four components: methanol, water, dimethyl dipicolinate and potassium hydroxide. Dipicolinic acid is a naturally occurring chemical (composes 5% to 15% of bacterial spores) and responsible for the heat resistance of bacterial endospore, and is cheap to purchase. On mixing with potassium hydroxide in 9 : 1 methanol-water, an instant transparent gel appeared. The most exciting fact is that the gelation is very selective for KOH only as other bases like NaOH, LiOH,  $K_2CO_3$ ,  $Na_2CO_3$ , and  $ET_3N$  fail to form any such type of gel under similar conditions. This suggests that both potassium and hydroxide ions have a significant role in the self-assembly process to form a soft gel phase material. In order to determine the optimal molar composition of the three variables (water, methanol and KOH), we first carried out an extensive three-variables screening defined by the ratio of water and methanol and the number of equivalents of KOH.

Initially, 6 mg (1 equiv.) of dimethyl dipicolinate (compound 1) and an excess of KOH (5 equiv.) were taken and the gelation ability was studied in 1 mL solvent by changing the ratio of water and methanol in a stepwise fashion. In workup methanol without any percentage of water, the compound fails to form a gel. Addition of water causes the formation of a soft gel material. When the ratio of water and methanol is 0.5 : 9.5, the compound forms a partial gel and half of the solvent remains free. The gelation ability increases with increasing ratio of water in methanol. The best gel is obtained when the ratio of water and methanol is 1 : 9. But after this ratio, further increase of water causes inhibition of gel formation (Fig. 1). When the ratio reaches 1.5 : 8.5, the whole of the system remains in a liquid phase without the formation of gel. The transparency of the gel material also increases with increase in the percentage of water in methanol (ESI Fig. 1†).

The gelation behaviour in the presence of other bases was also studied. Other bases including NaOH, LiOH,  $K_2CO_3$ ,  $Na_2CO_3$ , and  $ET_3N$  were also examined to address the question of whether any of them is able to form or induce the gelation. However, the compound 1 fails to form any kind of gel in the presence of the above-mentioned bases. This indicates that the gelation is extremely selective towards KOH. Moreover, the gelation of compound 1 was studied separately in  $K_2CO_3$  and LiOH to examine whether the presence of  $K^+$  or  $OH^-$  alone was sufficient for gel formation. But the compound fails to form

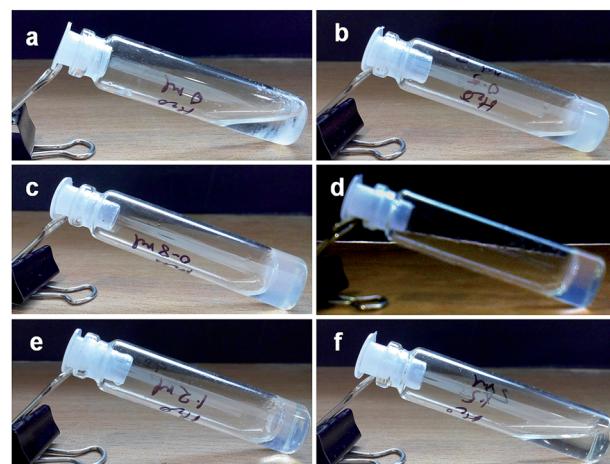


Fig. 1 Gelation study of compound 1 (6 mg, 1 equiv.) and KOH (5 equiv.) with various ratios of water and methanol (a) 0 : 10, (b) 0.5 : 9.5, (c) 0.8 : 9.2, (d) 1 : 9, (e) 1.2 : 8.8, and (f) 1.5 : 8.5.

a gel in  $K_2CO_3$  and LiOH separately. However, when these two bases were used together for a gelation study, the compound formed a gel (Fig. 2). This suggests that  $K_2CO_3$  and LiOH work as a source of  $K^+$  and  $OH^-$ , respectively, and the gelation is highly selective towards KOH. Hence  $K^+$  and  $OH^-$  ions have a significant effect in the self-assembly process of compound 1 in the gel state.

The composition and stoichiometry for gel formation were further studied by varying the equiv. of KOH. The minimum equivalent of KOH required for the gelation was screened by taking 20 mg of compound 1 in 1 mL of solvent (water and methanol, 1 : 9) and by increasing the equivalent of KOH from 0 to 5 equivalents to that of compound 1 (ESI Fig. 2†). It was found that a minimum of 3.5 equivalent of KOH was required for the gelation. The minimum gelation concentration (MGC) at room temperature was determined by using 3 equiv. of KOH and 1 : 9 water/methanol as the solvent. In a methanolic solution of compound 1, the addition of aqueous KOH (3

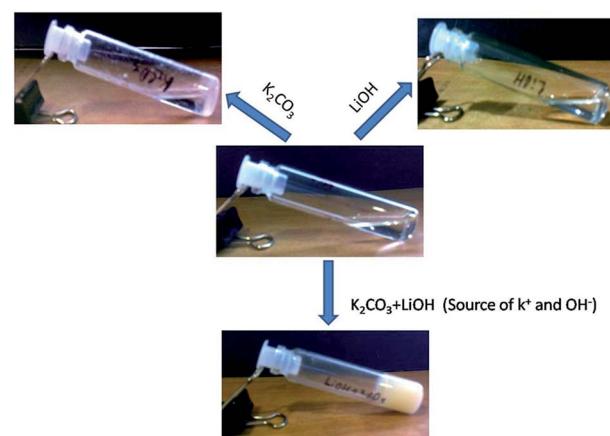


Fig. 2 Gelation study of compound 1 (2% w/v) in 1 : 9, ratio of water and methanol in the presence of  $K^+$  and  $OH^-$  ions.



equiv.), where the ultimate ratio of water/methanol is 1 : 9, instantly transforms it into a gel material without any external stimuli like heat or sonication. The minimum gelation concentration (MGC) was 0.5% w/v. The obtained gel material is not thermo-reversible and it is very stable at a comparatively high temperature.

A wide variety of alcoholic solvents were used to make the gel of compound **1** in the presence of KOH and water. However, the compound formed a gel only in methanol and ethanol. In other alcohols like 1-propanol, 2-propanol, and 1-butanol, the compound **1** fails to form a gel under the same conditions (Fig. 3). The gelation has been confirmed by the inverted vial method.<sup>49,50</sup> The opaque or transparent gels are stable for 2–3 months at room temperature. However, picolinic acid or monomethyl picolinate has failed to form a KOH responsive gel under the same conditions.

The visco-elastic properties of the gels were derived primarily from the tertiary structure by different rheological studies.<sup>51</sup> Rheology is the study of flow that provides information about the type of network (tertiary structure) responsible for the gelation. All the experiments were performed using a freshly prepared KOH responsive gel. By measuring the response of the soft material to an applied oscillatory stress, several variables can be resolved. The storage modulus ( $G'$ , a measure of the elastic response of the material) and loss modulus ( $G''$ , a measure of the viscous response) were measured as a function of shear stress and strain at 20 °C and a frequency of 10 rad s<sup>-1</sup>. For both the KOH responsive methanol and ethanol gel of compound **1**, the storage modulus ( $G'$ ) was found to be approximately an order of magnitude larger than the loss modulus ( $G''$ ), indicative of an elastic material and this is the comportment expected for a true gel phase (Fig. 4).  $G'$  and  $G''$  remain almost invariant with an increase in the applied stress. Throughout the experiment  $G'$  and  $G''$  do not cross each other, suggesting the presence of a stable and rigid gel phase material.

Thixotropic behaviour of gel was established by rheological measurements. A thixotropic gel is one which has the ability to disintegrate to solution or a quasi-liquid state under some external stimuli and can regain its original shape after the

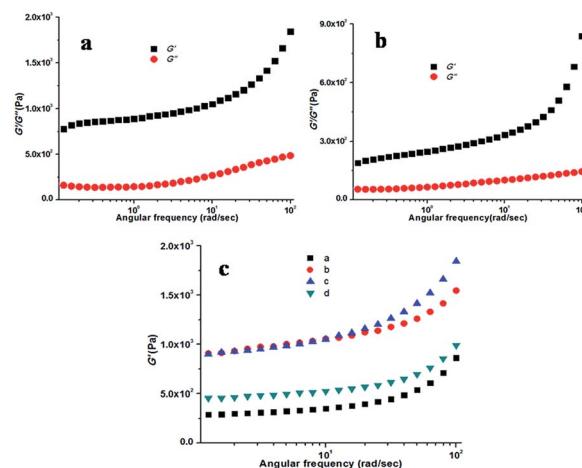


Fig. 4 Mechanical response of the KOH responsive gel of compound **1** in (a) MeOH–water and (b) EtOH–water at 20 °C with small oscillatory shear in the linear viscoelastic regime. (c) Rheological measurements of compound **1** gel with increasing percentage of water in methanol. Water : MeOH for *a* = 0.5 : 9.5, *b* = 0.8 : 9.2, *c* = 1 : 9 and *d* = 1.2 : 8.8.

removal of the applied stimuli. This process can be continued for several numbers of cycles *via* breaking and reconstructing the gels. In order to establish the thixotropic properties of the present gels, we have performed rheological step strain measurements<sup>52,53</sup> under varying strain at 20 °C. At first gels were subjected to a constant strain of 0.1%. At this strain  $G'$  is higher than  $G''$  (step 1, Fig. 5). Then the strain was increased from 0.1% to 30% and was kept for few minutes at 30% strain to break gels completely which was confirmed by complete inversion of  $G'$  and  $G''$  (step 2, Fig. 5). Then the strain was decreased from 30% to 0.1% again and kept for few minutes at 0.1% to observe the gel restoration kinetics (step 3, Fig. 5). After releasing the high strain the sol state again transformed into a semi-solid state and quickly regained its mechanical strength

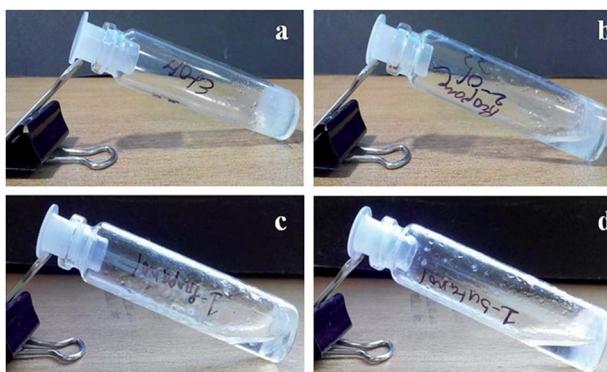


Fig. 3 Gelation study of compound **1** (2% w/v) and KOH (3.5 equiv.) in a 1 : 9 ratio of water and (a) ethanol, (b) 2-propanol, (c) 1-propanol, (d) 1-butanol.

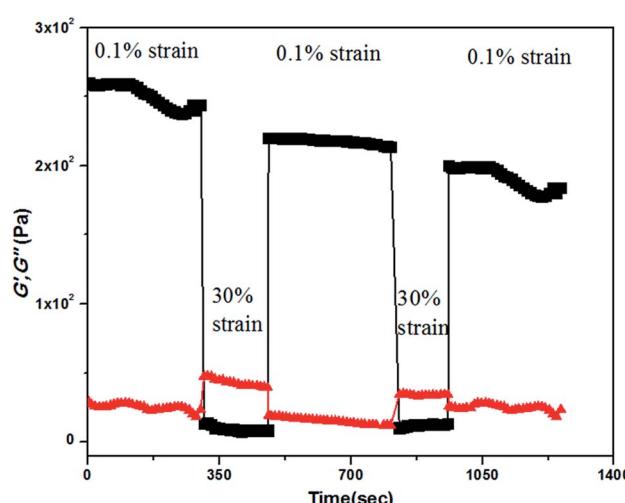


Fig. 5 The step strain experimental data obtained from the KOH responsive gel of compound **1** in 1 : 9 water : MeOH.



and we found almost 80% recovery at the low strain of 0.1%. This was continued for several cycles.

The morphological features of these KOH responsive gels were investigated by the field emission scanning electron microscopy studies (FE-SEM).<sup>54</sup> For FE-SEM experiments, to avoid any possible artefacts we executed experiments with a lowest KOH concentration containing diluted gel. The FE-SEM images of xerogel exhibit tape-like nanofibrillar network structures. The nanofibrills are polydisperse in nature and highly entangled. Interestingly, the fibres are twisted into helical structures (Fig. 6). Generally helical gel fibres are observed for chiral gelators, since chirality is often translated from the molecular level to the supramolecular level. However, compound **1** is not chiral and both left and right handed helical architectures are observed throughout the xerogel in every sample examined. In the absence of molecular chirality, the twisting may be responsible for the left and right handed helical architectures of the resultant fibers. The FE-SEM images of the xerogel obtained from different organic solvents show that the network morphology of peptide **1** does not vary from solvent to solvent.

Titration of compound **1** in 1 : 9 D<sub>2</sub>O/MeOD with increasing amount of KOH monitored by <sup>1</sup>H NMR spectroscopy provided evidence for the KOH compound **1** interaction. The aromatic proton signals of compound **1** exhibited further splitting without any change of integration and shifted gradually towards downfield with a gradual increase in KOH concentration, thus supporting the self-assembly through KOH compound **1** interactions (ESI Fig. 3†). A similar result was obtained by titration with LiOH (ESI Fig. 4†). Only, after the addition of 2.5 equivalents of LiOH, the aromatic proton signals of compound **1** return back to its original shape. The ester proton signal of compound **1** also shifted downfield with the addition of KOH or LiOH, without any change of integration suggesting that there is no ester hydrolysis under this condition. This is further supported by the existence of a FTIR signal at 1653 cm<sup>-1</sup>

responsible for ester carbonyls in both solution and xerogel (ESI Fig. 5†). Mass spectrometry of the xerogel has confirmed the absence of hydrolyzed products. Moreover, to gain better insight into the morphological evolution by KOH responsive compound **1** gel formation, X-ray diffraction experiments have been performed on the xerogel.<sup>55,56</sup> The powder X-ray diffraction (PXRD) pattern of the xerogel clearly shows that the material is crystalline in the xerogel and sharp reflections appeared in the 5–40° 2θ range. Sharp peaks appear at 2θ = 7.08 and 12.13 with long *d* spacing values of 12.47 Å and 7.29 Å, respectively (ESI Fig. 6†). These two peaks indicate the presence of a sheet-like packing arrangement.<sup>57–59</sup> A comparison of the spectrum obtained from the powder X-ray diffraction data of the xerogel and the powder pattern from X-ray crystallography of a single crystal of compound **1** and a single crystal of KOH clearly shows the significant differences and existence of KOH compound **1** interactions. Scanning electron microscopy images of the xerogels show twisted tape-like fibers. Energy-dispersive X-ray spectroscopy (EDS) experiments have been carried out for metal content determination of the xerogel. EDS confirms the potassium content (ESI Fig. 7†). Considering the above mentioned experiments a tentative model has been developed (ESI Fig. 8†).

Interestingly, the KOH responsive gels formed by compound **1** from water/methanol at a low concentration (1 wt%) are so stable that they can be shaped into any self-supporting geometrical shape using appropriate molds.<sup>60</sup> The gel could be handled with a tweezer or suspended in air just by holding one side (Fig. 7a). Also a big gel block can be sliced into various small pieces with a razor (Fig. 7b).<sup>61</sup> The KOH responsive gels formed by compound **1** from water/methanol at a low concentration (1 wt%) are sufficiently strong to tolerate the weight of several grams (Fig. 7c). More interestingly, these gels showed remarkable self-healing properties. When a block of gel was cut into two pieces and then joined together, the pieces merged into

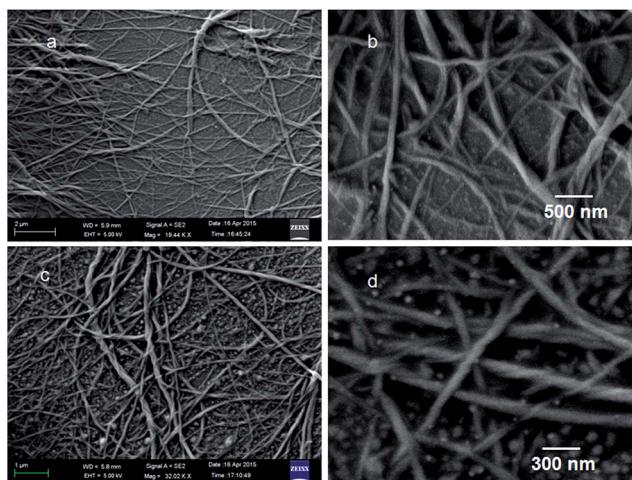


Fig. 6 The FE-SEM images of the xerogel showing a twisted fibrillar network structure of KOH responsive compound **1** gel in (a) and (b) 1 : 9 water : MeOH and (c) and (d) 1 : 9 water : EtOH.

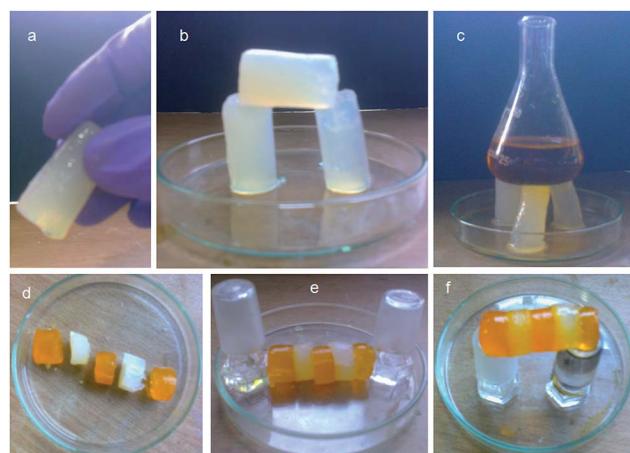


Fig. 7 (a) A gel cylinder taken in hand. (b) A gel gate made by fusing three stable gel cylinders. (c) The gel cylinders are sufficiently strong to tolerate the weight of several grams. (d) Alternate arrangement of methyl orange-doped and undoped gel cylinders. (e) Self-healing of the gel. (f) A cylinder made from five small gel discs suspended on two glass stoppers.



a continuous block.<sup>61</sup> Also, several small blocks of gels could be joined together to form a stable self-supporting bar. These fused bars could be taken in hand or suspended in air just by holding one side. The fusion of a methyl orange-doped gel with an undoped gel established the diffusion of methyl orange to the undoped piece, thus suggesting the dynamic exchange of dissolved molecules across the fusion interface (Fig. 7d–f). This self-healing process shows that the gel is living and dynamic in nature.<sup>62,63</sup> There is a dynamic equilibrium between continuous formation of new fibers and dissociation of old fibers. This movement would allow the growth of new fibers across the fusion interface and thus helps the repairing process.

The selectivity of compound **1** for forming a gel only in methanol or ethanol makes it an interesting candidate in separation of various miscible organic solvents.<sup>64</sup> If we have a mixture of ethyl acetate and methanol, we can separate the methanol by forming a gel. By the addition of a little amount of compound **1** and aqueous KOH to this ethyl acetate–methanol mixture, the compound will form a gel only with methanol and precipitate out. This gel can be removed easily from ethyl acetate by decantation or simple filtration (ESI Fig. 8†). Also the methanol can be collected by distillation of the gel. To the best of our knowledge this is the greenest way to separate miscible organic solvents.

To study the role of ester functional groups in compound **1** for gelation we have studied different analogues like mono acid mono ester and diacid of picolinic acid. In this regard we have studied compound **2** where monomethyl picolinate esters are separated by a spacer hexamethylenediamine. This compound does not form KOH responsive gels in a water/methanol mixture of any composition and even at a very high concentration. But, from X-ray crystallography, it is evident that the asymmetric unit contains two molecules of compound **2** and two molecules of water (ESI Fig. 10†). The hexamethylenediamine adopts all *anti*-conformation. There are two intramolecular five member hydrogen bonds between pyridine *N* and hexamethylenediamine NH (N2–H2···N1). The water molecule acts as a bridge between two molecules of compound **2** by two intermolecular hydrogen bonding interactions (O1S–H40···O2) and thereby forms a sheet-like structure in a higher order assembly (ESI Fig. 11†). We have correlated the crystal structure of compounds **1** and **2**. Compound **1** also shows a malty layer sheet-like structure in a higher order packing in the crystal (ESI Fig. 12†). As the ester oxygens involve in hydrogen bonding with water molecules, the compound **2** does not interact with KOH in a similar way as compound **1**. The compounds containing monomethyl picolinate and ethylenediamine<sup>65</sup> or propylenediamine<sup>66</sup> also failed to form KOH responsive gels in a water/methanol mixture.

Alcohols have been used as fuels for a long time and have high octane rating and some advantages over petrol and diesel. However, there are some limitations of using alcohols due to liquidity, high volatility, spilling and safety. Hence, converting the liquid alcohols into gels will be highly advantageous for easy handling, delivery and safety. On burning, the KOH responsive compound **1** methanol or ethanol gel does not produce any shoot, smoke, obnoxious odour and ash. The gelling agents are

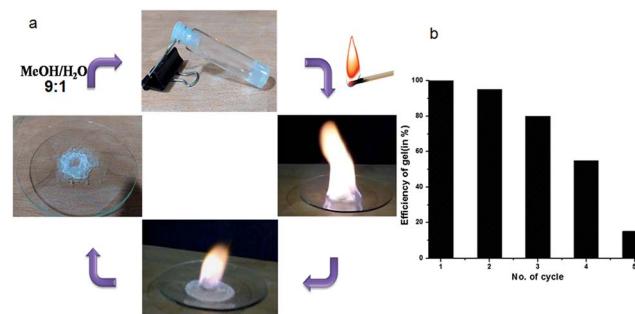


Fig. 8 (a) The burning methanol gel and recharge by 9 : 1 methanol–water. (b) Efficiency of gel after various cycles.

non-explosive, non-carcinogenic and non-corrosive. Due to its high mechanical strength, the gel can be shaped like any free-standing objects and can be packed in any container even in plastic jars, tubes and bottles. The gel exhibits remarkable self-healing properties. This dynamic nature of the gel made it practically useful as fuel-like paraffin. We found that the non explosive gel can be used as a safe fuel for indoor and outdoor heating without any special stove or burner (Fig. S13, ESI†). The KOH responsive compound **1** in ethanol has 1300 kJ mol<sup>−1</sup> heat of combustion compared to 726 kJ mol<sup>−1</sup> KOH for responsive compound **1** in methanol. Moreover, different organic colours (like methyl orange or rhodamine 6G) can be added to make the fuel gel colourful and more attractive. The gelator retains strong memory even after burning which makes it reusable up to four times by the addition of (9 : 1) methanol–water (Fig. 8). The compound **1** contained an ester segment, which was hydrolyzed by KOH in the burning process at high temperature and the gelation efficiency decreased with increasing burning cycles (Fig. S14, ESI†). The problem with other available normal heating–cooling alcoholic gels used as fuel gels is that with the start of burning the whole gel is converted to liquid and burns completely within a short time. As the KOH responsive compound **1** methanol or ethanol gel is not thermo-reversible and stable at high temperature, it remains in a gel phase at the time of burning and takes a long time to finish. Therefore the KOH responsive compound **1** methanol or ethanol gel is more user friendly and appealing to the consumers.

### 3. Experimental

#### General

All chemicals were purchased from Sigma chemicals.

#### Synthesis

The compound **1** was synthesized from picolinic acid by conventional methods. The compound **2** was synthesized from monomethyl picolinate and hexamethylenediamine by a solution-phase methodology. The products were purified by column chromatography using a silica (100–200 mesh size) gel as a stationary phase and an *n*-hexane–ethyl acetate mixture as an eluent. The compounds were fully characterized by 500 MHz <sup>1</sup>H NMR spectroscopy, 125 MHz <sup>13</sup>C NMR



spectroscopy, FTIR spectroscopy and mass spectrometry. The compounds **1** and **2** were characterized by X-ray crystallography.

### NMR experiments

All NMR studies were carried out on a Brüker AVANCE 500 MHz spectrometer. Compound concentrations were in the range of 1–10 mm in CD<sub>3</sub>OD, MeOD and D<sub>2</sub>O.

### FTIR spectroscopy

All reported solid-state FTIR spectra were obtained with a Perkin Elmer Spectrum RX1 spectrophotometer using the KBr disk technique and in MeOH solution.

### Mass spectrometry

Mass spectra were recorded on a Q-ToF Micro YA263 high-resolution (Waters Corporation) mass spectrometer by positive-mode electrospray ionization.

### Gelation

The compound **1** (dimethyl dipicolinate) (6 mg, 1 equiv.) and an excess of KOH (5 equiv.) were taken and the gelation ability was studied in 1 mL solvent by changing the ratio of water and methanol in a stepwise fashion at room temperature. An instant homogeneous gel appeared when the ratio of water and methanol is 1 : 9.

### Rheology

The viscoelastic properties of sonication induced gels were measured with a commercial rheometer (AR-G2, TA Instruments, New Castle, USA).

### Single crystal X-ray diffraction study

Intensity data were collected with MoK $\alpha$  radiation using a Bruker APEX-2 CCD diffractometer. Data were processed using the Bruker SAINT package and the structure solution and refinement procedures were performed using SHELX97. The non-hydrogen atoms were refined with anisotropic thermal parameters. The data have been deposited at the Cambridge Crystallographic Data Centre with reference CCDC 918260.

### Field emission scanning electron microscopy

Morphologies of the reported xerogel were investigated using field emission-scanning electron microscopy (FE-SEM). A small amount of sample was placed on a clean glass slide and then dried by slow evaporation. The material was then allowed to dry under vacuum at 30 °C for two days. The materials were gold-coated, and the micrographs were taken in an FE-SEM apparatus (Jeol Scanning Microscope-JSM-6700F).

## 4. Conclusions

In conclusion, we have developed a stimuli responsive organogelation system at room temperature based on dimethyl picolinate. The gelation is highly selective for potassium hydroxide.

Interestingly, the assembly of gelator molecules can effectively trap methanol or ethanol in the presence of water (9 : 1). The gel exhibits high stability, thixotropic behaviour and self-healing properties. The non-explosive gel can be used as a safe fuel for indoor and outdoor heating without any special stove or burner. The gelator retains strong memory even after burning which makes it rechargeable up to four times by the addition of (9 : 1) methanol–water. The eco-friendly gel can be shaped into any self-supporting geometrical shape, coloured with organic dyes and can be packed in any container which is appealing to the consumers.

## Acknowledgements

We acknowledge the CSIR, India, for financial assistance (Project No. 01/2507/11-EMR-II). S. Bera thanks the UGC, India for research fellowship.

## Notes and references

- 1 R. G. Weiss, *J. Am. Chem. Soc.*, 2014, **136**, 7519–7530.
- 2 J. Raeburn and D. J. Adams, *Chem. Commun.*, 2014, **51**, 5170–5180.
- 3 D. J. Cornwell and D. K. Smith, *Mater. Horiz.*, 2015, **2**, 279–293.
- 4 G. O. Lloyd and J. W. Steed, *Nat. Chem.*, 2009, **1**, 437–442.
- 5 L. A. Estroff and A. D. Hamilton, *Chem. Soc. Rev.*, 2004, **104**, 1201–1216.
- 6 G. Yu, X. Yan, C. Han and F. Huang, *Chem. Soc. Rev.*, 2013, **42**, 6697–6722.
- 7 L. E. Buerkle and S. J. Rowan, *Chem. Soc. Rev.*, 2012, **41**, 6089–6102.
- 8 J. W. Steed, *Chem. Commun.*, 2011, **47**, 1379–1383.
- 9 Y. Hisamatsu, S. Banerjee, M. B. Avinash, T. Govindaraju and C. Schmuck, *Angew. Chem., Int. Ed.*, 2013, **52**, 12550–12554.
- 10 K. L. Caran, D.-C. Lee and R. G. Weiss, Molecular Gels and Their Fibrillar Networks, in *Soft Fibrillar Materials: Fabrication and Applications*, ed. X. Y. Liu and J.-L. Li, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim, Germany, 2013.
- 11 R. G. Weiss and P. Terech, *Molecular Gels: Materials With Self-assembled Fibrillar Networks*, Springer, Dordrecht, The Netherlands, 2006.
- 12 S. R. Raghavan and J. F. Douglas, *Soft Matter*, 2012, **8**, 8539–8546.
- 13 A. S. Weingarten, R. V. Kazantsev, L. C. Palmer, M. McClendon, A. R. Koltonow, A. P. S. Samuel, D. J. Kiebala, M. R. Wasielewski and S. I. Stupp, *Nat. Chem.*, 2014, **6**, 964–970.
- 14 M. D. Segarra-Maset, V. J. Nebot, J. F. Miravet and B. Escuder, *Chem. Soc. Rev.*, 2013, **42**, 7086–7098.
- 15 G. M. Peters, L. P. Skala, T. N. Plank, H. Oh, G. N. M. Reddy, A. Marsh, S. P. Brown, S. R. Raghavan and J. T. Davis, *J. Am. Chem. Soc.*, 2015, **137**, 5819–5827.
- 16 M. Ikeda, T. Tanida, T. Yoshii, K. Kurotani, S. Onogi, K. Urayama and I. Hamachi, *Nat. Chem.*, 2014, **6**, 511–518.

- 17 M. Guo, L. M. Pitet, H. M. Wyss, M. Vos, P. Y. W. Dankers and E. W. J. Meijer, *J. Am. Chem. Soc.*, 2014, **136**, 6969–6977.
- 18 W. Guo, C.-H. Lu, X.-J. Qi, R. Orbach, M. Fadeev, H.-H. Yang and I. Willner, *Angew. Chem., Int. Ed.*, 2014, **53**, 10134–10138.
- 19 T. Yoshii, M. Ikeda and I. Hamachi, *Angew. Chem., Int. Ed.*, 2014, **53**, 7264–7267.
- 20 S. S. Babu, S. Prasanthkumar and A. Ajayaghosh, *Angew. Chem., Int. Ed.*, 2012, **51**, 1766–1776.
- 21 D. D. Diaz, D. Kuehbeck and R. J. Koopmans, *Chem. Soc. Rev.*, 2011, **40**, 427–448.
- 22 T. Yoshii, S. Onogi, H. Shigemitsu and I. Hamachi, *J. Am. Chem. Soc.*, 2015, **137**, 3360–3365.
- 23 G.-F. Liu, D. Zhang and C.-L. Feng, *Angew. Chem., Int. Ed.*, 2014, **53**, 7789–7793.
- 24 Y. Kuang, J. Shi, J. Li, K. A. Alberti, Q. Xu and B. Xu, *Angew. Chem., Int. Ed.*, 2014, **53**, 8104–8107.
- 25 L. E. Buerkle, H. A. von Recum and S. J. Rowan, *Chem. Sci.*, 2012, **3**, 564–572.
- 26 M. Ikeda, T. Yoshii, T. Matsui, T. Tanida, H. Komatsu and I. Hamachi, *J. Am. Chem. Soc.*, 2011, **133**, 1670–1673.
- 27 H. K. Lau and K. L. Kiick, *Biomacromolecules*, 2015, **16**, 28–42.
- 28 K. J. Skilling, F. Citossi, T. D. Bradshaw, M. Ashford, B. Kellam and M. Marlow, *Soft Matter*, 2014, **10**, 237–256.
- 29 N. M. Sangeeth and U. Maitra, *Chem. Soc. Rev.*, 2005, **34**, 821–836.
- 30 H. Svobodova, V. Noponen, E. Kolehmainen and E. Sievanen, *RSC Adv.*, 2012, **2**, 4985–5007.
- 31 Y. Li, B. Z. Li, Y. T. Fu, S. W. Lin and Y. G. Yang, *Langmuir*, 2013, **29**, 9721–9726.
- 32 K. Isozaki, H. Takaya and T. Naota, *Angew. Chem., Int. Ed.*, 2007, **46**, 2855–2857.
- 33 C. Kang, L. Wang, Z. Bian, H. Guo, X. Ma, X. Qiu and L. Gao, *Chem. Commun.*, 2014, **50**, 13979–13982.
- 34 L. E. R. O'Leary, J. A. Fallas, E. L. Bakota, M. K. Kang and J. D. Hartgerink, *Nat. Chem.*, 2011, **3**, 821–828.
- 35 J. W. Steed, *Chem. Soc. Rev.*, 2010, **39**, 3686–3699.
- 36 N. S. Vujicic, Z. Glasovac, N. Zweep, J. H. van Esch, M. Vinkovic, J. Popovic and M. Zinic, *Chem.-Eur. J.*, 2013, **19**, 8558–8572.
- 37 X. Wang and M. Liu, *Chem.-Eur. J.*, 2014, **20**, 10110–10116.
- 38 Z. Shen, T. Wang and M. Liu, *Angew. Chem., Int. Ed.*, 2014, **53**, 13424–13428.
- 39 S. J. James, A. Perrin, C. D. Jones, D. S. Yufit and J. W. Steed, *Chem. Commun.*, 2014, **50**, 12851–12854.
- 40 L. Meazza, J. A. Foster, K. Fucke, P. Metrangolo, G. Resnati and J. W. Steed, *Nat. Chem.*, 2013, **5**, 42–47.
- 41 J. Cui, J. Zheng, W. Qiao and X. Wan, *J. Colloid Interface Sci.*, 2008, **326**, 267–274.
- 42 J. Liu, Y. Feng, Z. Liu, Z. Yan, Y. He, C. Liu and Q. Fan, *Chem.-Asian J.*, 2013, **8**, 572–581.
- 43 Z. Ding, R. Xing, X. Wang, J. Ding, L. Wang and Y. Han, *Soft Matter*, 2013, **9**, 10404–10412.
- 44 S. S. Babu, V. K. Praveen and A. Ajayaghosh, *Chem. Rev.*, 2014, **114**, 1973–2129.
- 45 C. Kang, Z. Bian, Y. He, F. Han, X. Qiu and L. Gao, *Chem. Commun.*, 2011, **47**, 10746–10748.
- 46 A. A. Bredikhin, Z. A. Bredikhina, F. S. Akhatova and A. T. Gubaidullin, *Chem. Commun.*, 2010, **46**, 3523–3525.
- 47 Y. Ohsedo, M. Miyamoto, M. Oono, K. Shikii and A. Tanaka, *RSC Adv.*, 2013, **3**, 3844–3847.
- 48 P. W. J. M. Frederix, G. G. Scott, Y. M. Abul-Haija, D. Kalafatovic, C. G. Pappas, N. Javid, N. T. Hunt, R. V. Ulijn and T. Tuttle, *Nat. Chem.*, 2015, **7**, 30–37.
- 49 A. Pramanik, A. Paikar and D. Haldar, *RSC Adv.*, 2015, **5**, 53886–53892.
- 50 A. Paikar, A. Pramanik and D. Haldar, *RSC Adv.*, 2015, **5**, 31845–31851.
- 51 N. Yan, Z. Xu, K. K. Diehn, S. R. Raghavan, Y. Fang and R. G. Weiss, *J. Am. Chem. Soc.*, 2013, **135**, 8989–8999.
- 52 N. T. Qazvini, S. Bolisetty, J. Adamcik and R. Mezzenga, *Biomacromolecules*, 2012, **13**, 2136–2147.
- 53 S. Basak, J. Nanda and A. Banerjee, *Chem. Commun.*, 2014, **50**, 2356–2359.
- 54 Z. Ma, P. Zhang, X. Yu, H. Lan, Y. Li, D. Xie, J. Lib and T. Yi, *J. Mater. Chem. B*, 2015, **3**, 7366–7371.
- 55 Q. Jin, J. Li, L. Zhang, S. Fanga and M. Liu, *CrystEngComm*, 2015, **17**, 8058–8063.
- 56 M. Dubey, A. Kumar, R. K. Gupta and D. S. Pandey, *Chem. Commun.*, 2014, **50**, 8144–8147.
- 57 S. K. Samanta and S. Bhattacharya, *Chem. Commun.*, 2013, **49**, 1425–1427.
- 58 B. O. Okesola and D. K. Smith, *Chem. Commun.*, 2013, **49**, 11164–11166.
- 59 S. Basak, N. Nandi and A. Banerjee, *Chem. Commun.*, 2014, **50**, 6917–6919.
- 60 Q. Wang, J. L. Mynar, M. Yoshida, E. Lee, M. Lee, K. Okuro, K. Kinbara and T. Aida, *Nature*, 2010, **463**, 339–343.
- 61 A. Vidyasagar, K. Handore and K. M. Sureshan, *Angew. Chem., Int. Ed.*, 2011, **50**, 8021–8024.
- 62 X. Yu, L. Chen, M. Zhang and T. Yi, *Chem. Soc. Rev.*, 2014, **43**, 5346–5371.
- 63 Z. Xu, J. Peng, N. Yan, H. Yu, S. Zhang, K. Liu and Y. Fang, *Soft Matter*, 2013, **9**, 1091–1099.
- 64 S. Song, A. Song, L. Feng, G. Wei, S. Dong and J. Hao, *ACS Appl. Mater. Interfaces*, 2014, **6**, 18319–18328.
- 65 S. Bera, S. Maity and D. Haldar, *CrystEngComm*, 2015, **17**, 1569–1575.

