





Cite this: *Green Chem.*, 2020, **22**, 7560

Received 8th September 2020,  
Accepted 29th September 2020

DOI: 10.1039/d0gc03051a

[rsc.li/greenchem](http://rsc.li/greenchem)

## Electrodeposited Cu–Pd bimetallic catalysts for the selective electroreduction of CO<sub>2</sub> to ethylene†

Ruting Feng,<sup>a</sup> Qinggong Zhu,<sup>b</sup> Mengen Chu,<sup>a</sup> Shuaiqiang Jia,<sup>a</sup> Jianxin Zhai,<sup>a</sup> Haihong Wu,<sup>a</sup> \*<sup>a</sup> Peng Wu<sup>b</sup> \*<sup>a</sup> and Buxing Han<sup>b</sup> \*<sup>a,b</sup>

Cu–Pd bimetallic catalysts were fabricated on carbon paper (CP) by the electrodeposition method *via* a dynamic hydrogen bubble template approach. At a potential of  $-1.2$  V vs. RHE, the Faradaic efficiency (FE) of C<sub>2</sub>H<sub>4</sub> could reach 45.2% with a current density of 17.4 mA cm<sup>-2</sup> in an H-type electrolytic cell. Detailed studies suggest that the enhanced performance of Cu–Pd/CP was attributed mainly to the synergistic effect, low interfacial charge transfer resistance, and the 3D architecture of the catalysts.

Carbon dioxide (CO<sub>2</sub>) reduction has garnered intense interest with the global energy and environmental crises.<sup>1,2</sup> An ideal route for the chemical utilization of CO<sub>2</sub> is to develop catalytic processes for the selective conversion of CO<sub>2</sub> into value-added chemicals and fuels.<sup>3–5</sup> Among all the developed techniques, electrocatalytic reduction is a promising route for the utilization of CO<sub>2</sub> as a carbon feedstock to value-added chemicals.<sup>6–11</sup> To date, extensive efforts have been devoted to the development of electrocatalysts for the CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR) to higher value products.<sup>12–14</sup>

Ethylene (C<sub>2</sub>H<sub>4</sub>) is a popular chemical commodity used in industry.<sup>15,16</sup> Compared with C<sub>1</sub> products, C<sub>2</sub>H<sub>4</sub> possesses an impressive energy density and higher economic value.<sup>13,17,18</sup> Currently, copper (Cu) is the promising candidate as a catalyst that could produce C<sub>2</sub> products, but often a wide range of products are formed with low product selectivity.<sup>19,20</sup> To overcome the poor selectivity of pure Cu toward C<sub>2</sub> products, various strategies have been proposed, including alloying,<sup>21</sup> doping,<sup>22</sup> changing the composition and morphology, and creating special electrolytic devices.<sup>23</sup> For instance, Cu-doped carbon catalysts have been reported to enhance the electroreduction of CO<sub>2</sub> to C<sub>2</sub>H<sub>4</sub>.<sup>24</sup> Plasma-activated oxide derived-Cu (OD-Cu) catalysts with high stability of Cu<sup>+</sup> species have been reported to promote the C<sub>2</sub> product formation.<sup>25</sup> While significant progress has been achieved in the CO<sub>2</sub>RR to C<sub>2</sub>H<sub>4</sub>,<sup>26,27</sup> the explora-

tion of electrochemical systems for electrocatalytic C–C coupling in aqueous electrolytes is still an open challenge due to low selectivity, activity, and large overpotential.<sup>28–30</sup> The design of the catalyst holds the key to address these challenges.<sup>31,32</sup>

Recently, Cu-based bimetallic catalysts have shown great potential in enhancing the catalytic ability toward C<sub>2</sub> products by increasing strains and the synergistic effects of atoms in the catalyst.<sup>20,33,34</sup> Enhancement in the selectivity for C<sub>2</sub>H<sub>4</sub> has been observed on various bimetallic catalysts. For example, Au–Cu bimetallic catalysts have been investigated to increase the C<sub>2</sub>H<sub>4</sub> selectivity to 46.7%.<sup>35</sup> Ag–Cu nanoparticles showed a selectivity of the CO<sub>2</sub>RR toward C<sub>2</sub>H<sub>4</sub> with the FE of 41.3%.<sup>36</sup> Besides, the Cu–Ru bimetallic alloy could catalyze CO<sub>2</sub> conversion to C<sub>2</sub>H<sub>4</sub> with the FE of 19%.<sup>37</sup> The nanoporous Cu–Ag bimetallic catalyst was also reported to reduce CO<sub>2</sub> to C<sub>2</sub>H<sub>4</sub> with the FE of 60%.<sup>38</sup> However, even after such extensive research efforts, achieving high selectivity for C<sub>2</sub>H<sub>4</sub> on facilely-prepared bimetallic catalysts is still highly desired in this field.<sup>39,40</sup>

Self-supporting bimetallic catalysts by electrodeposition is a very useful technique that can form a three-dimensional (3D) porous structure and an increased surface area by a one-step strategy of potentiostatic co-electrodeposition utilizing hydrogen bubble dynamic templates.<sup>41,42</sup> Compared with other synthesized methods, the corresponding technology is often known as electroplating, which can simplify the experimental process, further reduce the cost and increase the electrode efficiency due to their extraordinary chemical properties in the electrolyte during the electrodeposition.<sup>43</sup> Electrocatalysts also provide some obvious advantages in the CO<sub>2</sub>RR, such as fast electron transfer rate, a large specific area and high electrochemical performance.<sup>12</sup>

In this work, we focus on enhancing the selectivity of the CO<sub>2</sub>RR to C<sub>2</sub>H<sub>4</sub> on Cu–Pd bimetallic catalysts, which were prepared by galvanostatic electrodeposition using the self-supporting technique. The resulting Cu–Pd bimetallic catalysts

<sup>a</sup>Shanghai Key Laboratory of Green Chemistry and Chemical Processes, School of Chemistry and Molecular Engineering, East China Normal University, Shanghai 200062, P. R. China. E-mail: hhwu@chem.ecnu.edu.cn, pwwu@chem.ecnu.edu.cn, hanbx@iccas.ac.cn

<sup>b</sup>Beijing National Laboratory for Molecular Sciences, CAS Key Laboratory of Colloid and Interface and Thermodynamics, CAS Research/Education Center for Excellence in Molecular Sciences, Institute of Chemistry, Chinese Academy of Sciences, Zhongguancun North First Street 2, Beijing, 100190, P. R. China

†Electronic supplementary information (ESI) available. See DOI: 10.1039/d0gc03051a

had a high selectivity toward  $C_2H_4$  (45.2%) at an applied potential of  $-1.2$  V vs. RHE and a current density of  $17.4$  mA  $cm^{-2}$  in aqueous electrolyte. The high catalytic activity of bimetallic Cu–Pd catalysts was attributed to the synergistic effect between Cu and Pd, fast electron transfer rate, and the 3D architecture of the catalyst.

The Cu–Pd bimetallic catalysts were synthesized by a facile electrodeposition method, which is schematically described in Fig. 1A. In the deposition process, Cu and Cu–Pd samples were electrodeposited in an acid solution containing  $Cu^{2+}$  and  $Pd^{2+}$  at pH = 1. During the deposition, the dynamic hydrogen bubble was used as a template to prepare functional porous materials. Cu–Pd was electrodeposited galvanostatically at a constant current density. The catalysts were characterized by scanning electron microscopy (SEM) and transmission electron microscopy (TEM). Fig. 1B–D provide the SEM images of CP, Cu/CP and Pd/CP. It is shown that a rough surface of Cu deposit and a half-baked dendritic 3D structure for Pd were formed on CP. Unlike these catalysts, Cu–Pd bimetallic catalysts show observable structural changes (Fig. 1E), and a tetrahedron structure was formed with nanostructured features on the scale of 90–200 nm (Fig. 1F, TEM). We also examined Cu–Pd/CP catalysts using elemental distribution mappings (EDS, Fig. 1G–I), which show that Cu (green) and Pd (red) atoms are homogeneously distributed, forming a bimetallic structure.


According to X-ray diffraction (XRD, Fig. 3A), the diffraction peak located at  $24.8^\circ$  was assigned to the (002) plane of the CP. Cu diffraction peaks of the (111), (200), and (220) facets are present for the bimetallic samples. The diffraction peaks of these samples had an appreciable shift in comparison with that of Pd. No Pd-related peaks were found, indicative of the low amount of Pd in the bimetallic catalysts. The Cu–Pd bi-

metallic samples also exhibited  $Cu_2O$  diffraction peaks of (110), (111), and (220), which are associated with the presence of the  $Cu_2O$  phase in the bimetallic catalysts.

X-ray photoelectron spectroscopy (XPS) further identified the elemental contents and valence states of Cu and Pd in the catalysts (Fig. 2B and C.). The results of XPS investigations on Cu/CP and Pd/CP are consistent with the results of XRD. For Cu–Pd/CP, it can be seen that the Cu/Pd ratio is 6.83, which indicates the formation of bimetallic catalysts (Table S1†). The binding energies of Cu 2p spectra were fitted with two components, which are  $Cu^I + Cu^0$  ( $2p_{3/2}$ , 932.4 eV;  $2p_{1/2}$ , 952.0 eV) and  $Cu^{II}$  ( $2p_{3/2}$ , 934.2 eV;  $2p_{1/2}$ , 954.0 eV), respectively. The intensities of Pd  $3d_{5/2}$  peaks of Cu–Pd catalysts at 337.2 eV and 337.8 eV correspond to the metallic  $Pd^0$  and  $Pd^{II}$ , and the Pd  $3d_{3/2}$  peaks at 342.5 eV and 342.8 eV correspond to  $Pd^0$  and  $Pd^{II}$ . This indicates that O species exist on the catalyst surface. The presence of O species may cause an enhancement in the  $C_2H_4$  production efficiency.<sup>38</sup>

The electrocatalytic performances of Cu–Pd/CP were investigated in  $CO_2$ -saturated KCl aqueous solution in a typical three-electrode electrochemical system. Linear sweep voltammetry (LSV) was conducted to investigate the performance of Cu–Pd in 0.1 M KCl aqueous solution, and the LSV curves were swept in the potential range from 0 to  $-1.4$  V (vs. RHE) at a sweep rate of  $50$  mV  $s^{-1}$ . As shown in Fig. 3A, Cu–Pd/CP exhibited a higher current density than other electrodes (CP, Pd/CP, and Cu/CP), suggesting that Cu–Pd bimetallic catalysts were favorable to the binding of  $CO_2$ . In addition, the much higher current density of the  $CO_2$ -saturated catholyte than the  $N_2$ -saturated catholyte implied the reduction of  $CO_2$  (Fig. S1†).


Controlled potential electrolysis was performed using a typical H-type electrolysis cell in the same system. After electrolysis, the gas and liquid products were analyzed by gas chromatography (GC) and nuclear magnetic resonance ( $^1H$ -NMR) analysis, respectively. The main gaseous products were  $C_2H_4$ ,  $H_2$  and a trace amount of  $CO$ ; no liquid product was detected

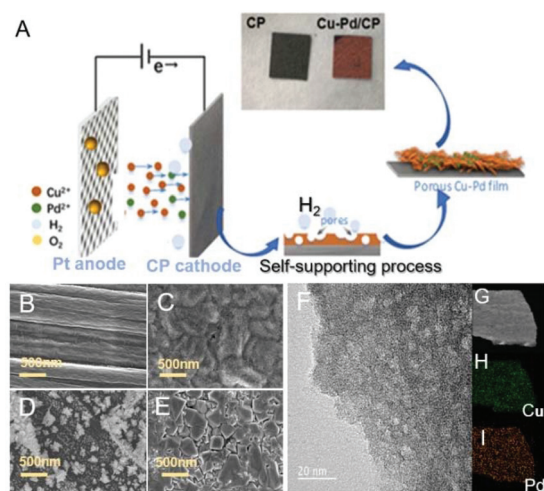

**Fig. 1** (A) Schematic illustration of the procedure for preparing Cu–Pd bimetallic catalysts; SEM images: (B) CP; (C) Cu/CP catalysts; (D) Pd/CP catalysts; (E) Cu–Pd/CP catalysts; (F) TEM image of Cu–Pd/CP catalysts; (G) the elemental mappings of Cu–Pd/CP catalysts. The images in green and red represent (H) Cu and (I) Pd, respectively.



**Fig. 2** (A) XRD patterns of Cu–Pd/CP, Cu/CP, Pd/CP, and CP; XPS spectra of (B) Cu 2p and (C) Pd 3d levels of catalysts.

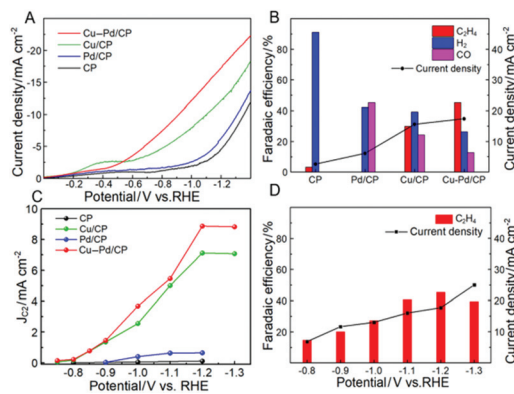

**Fig. 3** (A) LSV curves of various electrodes with a scan rate of  $50 \text{ mV}^{-1}$ ; (B) the FE of  $\text{C}_2\text{H}_4$  at  $-1.2 \text{ V}$  (vs. RHE) over various electrodes; (C) partial current density of  $\text{C}_2\text{H}_4$  over various electrodes at different applied potentials; (D) the FE and current density of  $\text{C}_2\text{H}_4$  over Cu–Pd/CP at different applied potentials in  $\text{CO}_2$ -saturated  $0.1 \text{ M KCl}$  solution.

by NMR. Fig. 3B shows the FE of the main products over various electrodes; it indicates that CP and Pd/CP have little catalytic effect on the electrocatalytic reduction of  $\text{CO}_2$  to  $\text{C}_2\text{H}_4$ . The main product on Pd/CP was syngas, which contains  $\text{H}_2$  and  $\text{CO}$ . On Cu/CP, the FE of  $\text{C}_2\text{H}_4$  was 29.97% with a CO FE of 24.3%. Among these samples, Cu–Pd/CP was the best catalyst with a  $\text{C}_2\text{H}_4$  FE of 45.23% at  $-1.2 \text{ V}$  (vs. RHE). Compared with the reported results using different bimetallic electrocatalysts (Table S2<sup>†</sup>), the FE and current density were high in the aqueous electrolyte using an H-type cell.

To gain kinetic insights into the  $\text{CO}_2\text{RR}$  to  $\text{C}_2\text{H}_4$  on Cu–Pd catalysts, the current density for  $\text{C}_2\text{H}_4$  at various overpotentials was measured. As shown in Fig. 3C, the onset potential over Cu–Pd/CP was  $-0.65 \text{ V}$ , which was more positive than those of Cu/CP ( $-0.72 \text{ V}$ ) and Pd/CP ( $-0.88 \text{ V}$ ), indicating that the initial electron transfer to  $\text{CO}_2$  to form an adsorbed  $\text{CO}_2^-$  intermediate was much easier over Cu–Pd/CP.<sup>44</sup> We also studied the change of  $\text{C}_2\text{H}_4$  over Cu–Pd/CP at different applied potentials. As the electrolytic potential increased, the FE of  $\text{C}_2\text{H}_4$  increased first and then decreased. The FE of  $\text{C}_2\text{H}_4$  reached 45.2% with a current density of  $17.4 \text{ mA cm}^{-2}$  at  $-1.2 \text{ V}$  vs. RHE (Fig. 3D). The decrease in the FE of  $\text{C}_2\text{H}_4$  at a high applied potential resulted from the enhancement in the production rate of  $\text{H}_2$ .

The electrochemical activity of Cu–Pd/CP was also characterized according to the Randle–Sevcik equation. The reduction current density plotted against the root of the scan rate is illustrated in Fig. S2.<sup>†</sup> According to the result, the Cu–Pd/CP has the largest slope among the electrodes, indicating the highest reduction rate for the  $\text{CO}_2\text{RR}$ . This result is consistent with the electrochemical impedance spectroscopy (EIS) result (Fig. S3<sup>†</sup>–4), which provides the charge transfer rate at the electrode/electrolyte interface. The results indicated that the charge transfer resistance ( $R_{ct}$ ) of the Cu–Pd/CP was lower than that of the Cu/CP. The above result shows that Pd or Cu could not promote the generation of the  $\text{C}_2\text{H}_4$  product efficiently, and

the excellent performance of Cu–Pd/CP can be attributed to the synergistic effect between Cu and Pd in the catalysts. On one hand, Cu-based bimetallic catalysts have shown great potential in enhancing the catalytic ability toward  $\text{C}_2$  products by increasing strains and the synergistic effects of atoms in the catalyst. Oxygen-bearing Cu catalysts could enable the C–C coupling in the electrocatalytic  $\text{CO}_2\text{RR}$  systems. The mixed valence form of copper ( $\text{Cu}^0$  and  $\text{Cu}^{\text{I}}$ ) may be the dominant species during the  $\text{CO}_2\text{RR}$ , which could be the most active species for the  $\text{C}_2$  product formation. The  $\text{Cu}^+/\text{Cu}^0$  interfaces formed through stabilized  $\text{Cu}^+$  facilitate the  $^*\text{CO}$ – $\text{CO}$  dimerization, promoting the formation of  $\text{C}_{2+}$  products and suppressing the conversion to  $\text{C}_1$  products. On the other hand, Pd is known to be an excellent catalyst for the  $\text{CO}_2\text{RR}$  to  $\text{CO}$ .<sup>21,40</sup> A trace amount of Pd could promote the adsorption of the  $^*\text{CO}$  intermediate and facilitate their dimerization to form  $\text{C}_2$  products.<sup>38,45</sup>

We also studied the electrolyte effect over the Cu–Pd/CP electrode. In addition to  $0.1 \text{ M KCl}$  electrolyte, other electrolytes that contain different cations and anions were used in this work (Fig. S5<sup>†</sup>). For example, in the  $\text{NaCl}$  electrolyte,  $\text{H}_2$  was the main product.  $\text{CO}_2\text{RR}$  exhibited better performance for  $\text{C}_2\text{H}_4$  with the FE of 35% in  $0.1 \text{ M KHCO}_3$  electrolyte. In  $0.1 \text{ M KH}_2\text{PO}_4$  and  $\text{K}_2\text{HPO}_4$  electrolyte, the FE of  $\text{C}_2\text{H}_4$  was very low with  $\text{H}_2$  as the main product. In the  $\text{KCl}$  electrolyte, even if the electrolyte concentration is increased, the FE of  $\text{C}_2\text{H}_4$  did not increase significantly, which indicates that  $0.1 \text{ M KCl}$  was the best electrolyte. We think that the electrolyte affects  $\text{CO}_2$  reduction mainly in two ways. First, the alkali metal cation (such as  $\text{Na}^+$ ,  $\text{K}^+$ ) in the electrolyte is known to influence the electrocatalytic ability of  $\text{CO}_2$  reduction. Density functional theory (DFT) calculations have shown that the alkali metal cations influence the distribution of products formed as a consequence of the electrostatic interactions between the solvated cations present at the outer Helmholtz plane and the adsorbed species having large dipole moments. Therefore, an increased alkali metal size leads to higher selectivity to  $\text{C}_2$  products.<sup>46,47</sup> Second, the local buffering capability of cations could increase the rate of the proton-transfer reaction, which affects the activity and selectivity for the  $\text{CO}_2\text{RR}$ . When the cation concentration was too low or too high, it will inhibit the proton-transfer reaction. Therefore, a moderate concentration facilitates proton transfer and improves the catalytic activity and selectivity.<sup>48,49</sup> These arguments are consistent with our experimental results.

We assume that the excellent activity of Cu–Pd bimetallic catalysts toward  $\text{C}_2\text{H}_4$  resulted from the synergistic effect of Cu and Pd in Cu–Pd catalysts. Therefore, we prepared the Cu–Pd catalysts using different electrodeposition methods (CV and amperometric mode), which may contain different atomic ratios of the elements (Table S1<sup>†</sup>). The corresponding electrodes were then named Cu–Pd/CP-CV and Cu–Pd/CP-IT (see the Experimental section in the ESI<sup>†</sup>). The SEM image of Cu–Pd/CP-CV and Cu–Pd/CP-IT electrodes showed a symmetrical and a homogeneous morphology, respectively (Fig. S6<sup>†</sup>). After electrolysis, we found that the FE of  $\text{C}_2\text{H}_4$  was approximately 25%

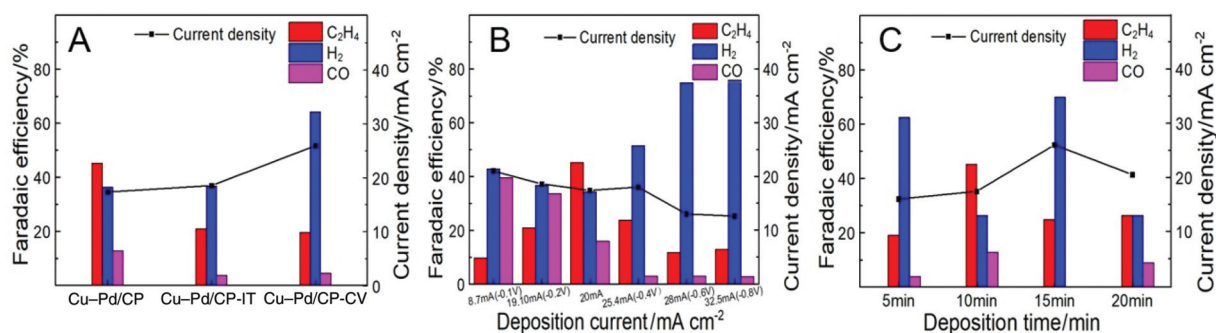


Fig. 4 The FE of  $C_2H_4$  over Cu–Pd bimetallic catalysts (A) using different electrodeposition methods; (B) under different current densities; (C) obtained at various deposition times.

over both electrodes with high hydrogen evolution reaction (HER) than the Cu–Pd/CP electrode (Fig. 4A). Therefore, we characterized the Cu–Pd catalysts prepared using different methods by XRD (Fig. S7†) and XPS (Fig. S8†) to get more information about the surface elemental states and catalytic performance. Among the three methods, Cu–Pd/CP showed the lowest  $(Cu^0 + Cu^I)/Cu^{II}$  and  $Pd^0/Pd^{II}$  ratio, which suggests the existence of oxygen vacancies in the catalysts (Table S1†). Therefore, it is beneficial for the adsorption of the intermediates and facilitates the formation of  $C_2H_4$ . The EIS results (Fig. S9, Table S3†) also showed that Cu–Pd/CP had a lower  $R_{ct}$  (Nyquist plot) and a larger phase angle in the low-frequency region (Bode plot) than that of Cu–Pd/CP-CV and Cu–Pd/CP-IT, resulting in the increase of electron transfer and the diffusion ability of Cu–Pd/CP.

The effect of deposition current density on the properties of the catalysts was also studied. The deposition of Cu–Pd bimetallic catalysts under different current densities not only affected the co-deposition process, but also changed the morphology of the catalyst. Therefore, we fixed the total amount of electrons to 12 Coulomb and obtained Cu–Pd catalysts with different morphologies under different current densities (Fig. S10†). Fig. 4B shows that the deposition current density of Cu–Pd catalysts had a great influence on the FE of  $C_2H_4$ . It may be due to the different atomic amounts in the catalysts. As shown in Fig. S11,† the bimetallic solution has an intermediate potential between the other two monometallic solutions. It indicates that at a high deposition potential and high current density, the deposition tended to deposit Cu. At a low deposition potential and low current density, the content of Pd in the catalysts increased. According to this tendency, the FE of  $C_2H_4$  was first increased and then decreased with increasing deposition current density, which indicates that an appropriate Cu–Pd ratio was beneficial for the reaction. This can also be known from the fact that the FE of  $C_2H_4$  over electrodeposited Cu/CP or Pd/CP was much lower (Fig. 3B).

The excellent activity of Cu–Pd catalysts may also result partially from the 3D architecture of the film. Therefore, we performed the  $CO_2$  reduction using Cu–Pd catalysts obtained at various deposition times. Fig. S12† shows that the amount of

the catalyst increased with increasing deposition time. The  $CO_2RR$  current density increased continuously with deposition time, but the FE of  $C_2H_4$  first increased and then decreased (Fig. 4C). This can be explained by the fact that the 3D structure gradually formed with increasing deposition time. This structure may provide more opportunities for the C–C coupling for the intermediates. When the film of the 3D structure was thick enough (>10 min), excessive catalyst agglomeration was not conducive to the reaction.

## Conclusion

In summary, we developed a facile electrodeposition method to fabricate Cu–Pd catalysts onto conductive substrates through the dynamic hydrogen bubble template approach. The synthesized Cu–Pd/CP is a highly effective catalyst for  $CO_2$  reduction to  $C_2H_4$ . The FE and current density of  $C_2H_4$  could reach 45.23% and  $17.4 \text{ mA cm}^{-2}$  in 0.1 M KCl aqueous electrolyte, respectively. A detailed study indicates that the synergistic effect between Cu and Pd in the Cu–Pd catalysts, low interfacial charge transfer resistance, the 3D architecture of the catalysts, and a suitable electrolyte are all favourable for the formation of  $C_2H_4$ . We believe that the strategy to prepare bimetallic catalysts by co-electrodeposition coupled with an effective electrolyte can be used to design more efficient catalytic systems for  $CO_2$  reduction to  $C_2$  products.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The work was supported by the National Natural Science Foundation of China (21533011, 21733011), the National Key Research and Development Program of China (2017YFA0403102), and the Chinese Academy of Sciences (QYZDY-SSW-SLH013).

## Notes and references

- M. He, Y. Sun and B. Han, *Angew. Chem., Int. Ed.*, 2013, **52**, 9620–9633.
- Z. Sun, T. Ma, H. Tao, Q. Fan and B. Han, *Chem*, 2017, **3**, 560–587.
- W. Lu, B. Jia, B. Cui, Y. Zhang, K. Yao, Y. Zhao and J. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 11851–11854.
- S. A. Abbas, S.-H. Kim, H. Saleem, S.-H. Ahn and K.-D. Jung, *Catalysts*, 2019, **9**, 367.
- L. Fan, C. Xia, F. Yang, J. Wang, H. Wang and Y. Lu, *Sci. Adv.*, 2020, **6**, eaay3111.
- Q. Zhu, J. Ma, X. Kang, X. Sun, J. Hu, G. Yang and B. Han, *Sci. China: Chem.*, 2016, **59**, 551–556.
- H. Yang, L. Wu, H. Wang and J. Lu, *Chin. J. Catal.*, 2016, **37**, 994–998.
- A. Loiudice, P. Lobaccaro, E. A. Kamali, T. Thao, B. H. Huang, J. W. Ager and R. Buonsanti, *Angew. Chem., Int. Ed.*, 2016, **55**, 5789–5792.
- X. Kang, Q. Zhu, X. Sun, J. Hu, J. Zhang, Z. Liu and B. Han, *Chem. Sci.*, 2016, **7**, 266–273.
- Y. Chen and T. Mu, *Green Chem.*, 2019, **21**, 2544–2574.
- X. Sun, Q. Zhu, X. Kang, H. Liu, Q. Qian, Z. Zhang and B. Han, *Angew. Chem., Int. Ed.*, 2016, **55**, 6771–6775.
- P. Moreno-García, N. Schlegel, A. Zanetti, A. Cedeño López, M. d. J. Galvez-Vazquez, A. Dutta, M. Rahaman and P. Broekmann, *ACS. Appl. Mater. Interfaces*, 2018, **10**, 31355–31365.
- A. Eilert, F. S. Roberts, D. Friebel and A. Nilsson, *J. Phys. Chem. Lett.*, 2016, **7**, 1466–1470.
- Z. Q. Liang, T. T. Zhuang, A. Seifitokaldani, J. Li, C. W. Huang, C. S. Tan, Y. Li, P. De Luna, C. T. Dinh, Y. Hu, Q. Xiao, P. L. Hsieh, Y. Wang, F. Li, R. Quintero-Bermudez, Y. Zhou, P. Chen, Y. Pang, S. C. Lo, L. J. Chen, H. Tan, Z. Xu, S. Zhao, D. Sinton and E. H. Sargent, *Nat. Commun.*, 2018, **9**, 3828.
- F. S. Roberts, K. P. Kuhl and A. Nilsson, *Angew. Chem., Int. Ed.*, 2015, **54**, 5179–5182.
- S. Sen, D. Liu and G. T. R. Palmore, *ACS. Catal.*, 2014, **4**, 3091–3095.
- C. W. Li and M. W. Kanan, *J. Am. Chem. Soc.*, 2012, **134**, 7231–7234.
- Z. Tan, T. Peng, X. Tan, W. Wang, X. Wang, Z. Yang, H. Ning, Q. Zhao and M. Wu, *ChemElectroChem*, 2020, **7**, 2020–2025.
- Y. Zheng, A. Vasileff, X. Zhou, Y. Jiao, M. Jaroniec and S. Z. Qiao, *J. Am. Chem. Soc.*, 2019, **141**, 7646–7659.
- C. Chen, X. Sun, L. Lu, D. Yang, J. Ma, Q. Zhu, Q. Qian and B. Han, *Green Chem.*, 2018, **20**, 4579–4583.
- S. Ma, M. Sadakiyo, M. Heima, R. Luo, R. T. Haasch, J. I. Gold, M. Yamauchi and P. J. Kenis, *J. Am. Chem. Soc.*, 2017, **139**, 47–50.
- Y. Zhou, F. Che, M. Liu, C. Zou, Z. Liang, P. De Luna, H. Yuan, J. Li, Z. Wang, H. Xie, H. Li, P. Chen, E. Bladt, R. Quintero-Bermudez, T. K. Sham, S. Bals, J. Hofkens, D. Sinton, G. Chen and E. H. Sargent, *Nat. Chem.*, 2018, **10**, 974–980.
- J. Du, S. Li, S. Liu, Y. Xin, B. Chen, H. Liu and B. Han, *Chem. Sci.*, 2020, **11**, 5098–5104.
- H. Ning, X. Wang, W. Wang, Q. Mao, Z. Yang, Q. Zhao, Y. Song and M. Wu, *Carbon*, 2019, **146**, 218–223.
- H. Mistry, A. S. Varela, C. S. Bonifacio, I. Zegkinoglou, I. Sinev, Y. W. Choi, K. Kisslinger, E. A. Stach, J. C. Yang, P. Strasser and B. R. Cuenya, *Nat. Commun.*, 2016, **7**, 12123.
- D. Ren, Y. Deng, A. D. Handoko, C. S. Chen, S. Malkhandi and B. S. Yeo, *ACS. Catal.*, 2015, **5**, 2814–2821.
- J.-C. Lee, J.-Y. Kim, W.-H. Joo, D. Hong, S.-H. Oh, B. Kim, G.-D. Lee, M. Kim, J. Oh and Y.-C. Joo, *J. Mater. Chem. A*, 2020, **8**, 11632–11641.
- D. Raciti, K. J. Livi and C. Wang, *Nano Lett.*, 2015, **15**, 6829–6835.
- L. Zhang, Z. J. Zhao and J. Gong, *Angew. Chem., Int. Ed.*, 2017, **56**, 11326–11353.
- K. Yao, Y. Xia, J. Li, N. Wang, J. Han, C. Gao, M. Han, G. Shen, Y. Liu, A. Seifitokaldani, X. Sun and H. Liang, *J. Mater. Chem. A*, 2020, **8**, 11117–11123.
- F. Li, L. Chen, G. P. Knowles, D. R. MacFarlane and J. Zhang, *Angew. Chem., Int. Ed.*, 2017, **56**, 505–509.
- X. Wang, Z. Chen, X. Zhao, T. Yao, W. Chen, R. You, C. Zhao, G. Wu, J. Wang, W. Huang, J. Yang, X. Hong, S. Wei, Y. Wu and Y. Li, *Angew. Chem., Int. Ed.*, 2018, **57**, 1944–1948.
- M. J. Mao, M. D. Zhang, D. L. Meng, J. X. Chen, C. He, Y. B. Huang and R. Cao, *ChemCatChem*, 2020, **12**, 3530–3536.
- S. Jia, Q. Zhu, H. Wu, M. e. Chu, S. Han, R. Feng, J. Tu, J. Zhai and B. Han, *Chin. J. Catal.*, 2020, **41**, 1091–1098.
- Y. Chen, Z. Fan, J. Wang, C. Ling, W. Niu, Z. Huang, G. Liu, B. Chen, Z. Lai, X. Liu, B. Li, Y. Zong, L. Gu, J. Wang, X. Wang and H. Zhang, *J. Am. Chem. Soc.*, 2020, **142**, 12760–12766.
- J. Huang, M. Mensi, E. Oveisi, V. Mantella and R. Buonsanti, *J. Am. Chem. Soc.*, 2019, **141**, 2490–2499.
- J. T. Billy and A. C. Co, *Appl. Catal., B*, 2018, **237**, 911–918.
- T. T. H. Hoang, S. Verma, S. Ma, T. T. Fister, J. Timoshenko, A. I. Frenkel, P. J. A. Kenis and A. A. Gewirth, *J. Am. Chem. Soc.*, 2018, **140**, 5791–5797.
- L. Lu, X. Sun, J. Ma, D. Yang, H. Wu, B. Zhang, J. Zhang and B. Han, *Angew. Chem., Int. Ed.*, 2018, **57**, 14149–14153.
- D. Chen, Q. Yao, P. Cui, H. Liu, J. Xie and J. Yang, *ACS Appl. Energy Mater.*, 2018, **1**, 883–890.
- B. J. Plowman, L. A. Jones and S. K. Bhargava, *Chem. Commun.*, 2015, **51**, 4331–4346.
- X. Lu and C. Zhao, *Nat. Commun.*, 2015, **6**, 6616.
- P. Ganesan, A. Sivanantham and S. Shanmugam, *ACS. Appl. Mater. Interfaces.*, 2017, **9**, 12416–12426.
- Q. Zhu, X. Sun, D. Yang, J. Ma, X. Kang, L. Zheng, J. Zhang, Z. Wu and B. Han, *Nat. Commun.*, 2019, **10**, 3851.
- T. Takashima, T. Suzuki and H. Irie, *Electrochim. Acta*, 2017, **229**, 415–421.

- 46 J. Resasco, L. D. Chen, E. Clark, C. Tsai, C. Hahn, T. F. Jaramillo, K. Chan and A. T. Bell, *J. Am. Chem. Soc.*, 2017, **139**, 11277–11287.
- 47 A. S. Varela, W. Ju, T. Reier and P. Strasser, *ACS. Catal.*, 2016, **6**, 2136–2144.
- 48 M. R. Singh, Y. Kwon, Y. Lum, J. W. Ager 3rd and A. T. Bell, *J. Am. Chem. Soc.*, 2016, **138**, 13006–13012.
- 49 J. Fu, W. Zhu, Y. Chen, Z. Yin, Y. Li, J. Liu, H. Zhang, J. J. Zhu and S. Sun, *Angew. Chem., Int. Ed.*, 2019, **58**, 14100–14103.