

# Polymer Chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: E. Voutyritsa, T. Lazou, J. Bushi, S. Margaritaki, M. Charitaki, S. M. Christensen, N. Hatzakis and K. Velonia, *Polym. Chem.*, 2024, DOI: 10.1039/D4PY00407H.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Data availability

The data supporting this article have been included as part of the Supplementary Information.



## ARTICLE

**Oxygen-tolerant, Eosin Y mediated synthesis of protein-polymer biohybrids and protein-coated polymer nanoparticles**Errika Voutyritsa,<sup>a, b, c, †</sup> Thomai Lazou,<sup>a, †</sup> Jonida Bushi,<sup>a, †</sup> Stavroula Margaritaki,<sup>a</sup> Myrto Charitaki,<sup>a</sup> Sune M. Christensen,<sup>d</sup> Nikos Hatzakis,<sup>b, c</sup> and Kelly Velonia<sup>\* a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

To avoid the use of metal catalysts used in conventional approaches, an Eosin Y/TEMED mediated, photoinduced polymerization of vinyl monomers was optimized for the synthesis of protein-polymer conjugates. This oxygen tolerant, photoinduced approach allowed to graft a series of hydrophobic, hydrophilic and responsive polymers with quantitative protein macroinitiator consumption. CALB bioconjugates were also synthesized and found to retain part of the parent protein activity for extended periods of time. Notably, when BSA was used in the absence of initiator, protein-coated nanoparticles were shown to form during emulsion polymerization.

**Introduction**

Protein-polymer conjugates are hybrid macromolecules aiming to combine the unique functions and properties encoded in biomolecules with the limitless physicochemical and functional adaptability of synthetic polymers. As such, they have been systematically pursued over several decades.<sup>1–3</sup> The vast range of potential applications of protein-polymer conjugates was first demonstrated with the synthesis of dextran-hemoglobin hybrids<sup>4</sup> and the PEGylation of bovine serum albumin (BSA).<sup>5–7</sup> The increased biocompatibility, stability and *in vivo* half-life of the first hybrid biomolecules sparked numerous investigations which have resulted in quite a few approved therapeutics by the United States Food and Drug Administration (FDA),<sup>8–10</sup> and systems designed to address scientific goals in drug delivery,<sup>11–16</sup> gated transport,<sup>17</sup> sensing and detection,<sup>18</sup> and catalysis.<sup>19–21</sup> Recent advances in polymer synthesis fostered significant progress also in polymer bioconjugate synthesis. In the early synthesis of protein-polymer conjugates, most reports employed grafting-to approaches involving amino acid-specific or random couplings of prefunctionalized polymers to the protein<sup>22–24</sup> or bioaffinity couplings.<sup>25–27</sup> More recently, by capitalizing on the ability to synthesize polymers in rapid, efficient, and precise manners,<sup>28</sup> numerous new methodologies have emerged for the synthesis of protein-polymer conjugates.<sup>2, 29–33</sup> These are mostly grafting-from methodologies involving controlled radical polymerization

(CRP) approaches such as atom transfer radical polymerization (ATRP),<sup>34–41</sup> Cu(O)-mediated radical polymerization,<sup>42–43</sup> and ring-opening polymerization,<sup>44–45</sup> as well as reversible addition-fragmentation chain transfer (RAFT)<sup>46–48</sup> polymerization approaches and chain growth polymerization techniques.

Very recent reports on the synthesis of protein-polymer conjugates focus on oxygen tolerant<sup>49–52</sup> and photomediated metal catalyzed approaches.<sup>39, 51, 53</sup> A significant advantage of photochemical approaches is that they offer temporal and spatial control under mild reaction conditions while oxygen tolerance is fundamental for the development of sustainable applications.<sup>54–57</sup> However, several of these approaches require metal-based catalysts and metal contamination is a limiting factor when aiming at biomedical applications. For this reason, the metal-free organocatalyzed ATRP (O-ATRP)<sup>58–61</sup> mediated synthesis of protein-polymer conjugates recently reported in seminal works by the groups of Sumerlin,<sup>62–63</sup> Matyjaszewski,<sup>64</sup> and Boyer<sup>65</sup> provides a new, powerful tool in the realms of oxygen tolerant bioconjugation. In this respect, the commonly used xanthene electron acceptor derivative, Eosin Y (EY), has been used as the organocatalyst as it is known to mediate photoinduced polymerization of several families of monomers in conjunction with alkyl halides and amines.<sup>66–68</sup> EY is cheap, commercially available, displays excellent biocompatibility and has therefore been widely used in biological applications.<sup>69–70</sup> Taking these beneficial characteristics into account, Sumerlin and collaborators were the first to employ EY-catalyzed PET-RAFT for the synthesis of polymer-protein conjugates in the presence of a tertiary amine and under visible-light irradiation.<sup>62–63</sup> Following this grafting-from approach, rapid synthesis of water soluble biohybrids over a range of targeted molecular weights was possible. In a more recent contribution, Eosin Y acrylate was copolymerized with N-isopropylacrylamide (NIPAM) to afford a polymeric photocatalyst with temperature dependent hydrophilic-to-hydrophobic transition which enabled easy purification of the bioconjugates post

<sup>a</sup> Department of Materials Science and Engineering, University of Crete, University Campus Voutes, 70013 Heraklion, Crete, Greece

<sup>b</sup> Department of Chemistry, University of Copenhagen

<sup>c</sup> NovoNordisk center for Optimised Oligo escape University of Copenhagen, Denmark

<sup>d</sup> Novonesis A/S, Biologiens Vej 2, 2800 Kgs. Lyngby, Denmark

<sup>†</sup> These authors contributed equally to this work.

Electronic Supplementary Information (ESI) available: details of any supplementary information available should be included here. See DOI: 10.1039/x0xx00000x



polymerization and recovery of the catalyst.<sup>63</sup> Importantly ascorbic acid (AsCA) was shown to efficiently deoxygenate the polymerization solution. Matyjaszewski and collaborators, developed green-light-induced dual catalysis ATRP, *i.e.*, using EY in combination with a copper complex which enabled rapid and well-controlled polymerization in water without the need for deoxygenation.<sup>71-72</sup> Following this approach, hydrophilic acrylate-based protein-polymer hybrids were also synthesized under ambient conditions.<sup>64</sup> Finally, Boyer and collaborators,<sup>65</sup> developed a photo-RAFT system allowing the synthesis of protein-polymer conjugates with excellent oxygen tolerance. During this study, the photocatalyst EY was combined with the reactive oxygen species (ROS) generating cocatalysts AsCA and triethanolamine (TEOA). Evaluation of the impact of the ROS on model proteins led to selection of EY/TEOA as the optimal photo-RAFT initiating system for preserving enzymatic activity.

Inspired by these reports, we developed an oxygen tolerant, EY photocatalyzed, grafting-from approach for the synthesis of protein-polymer conjugates in the absence of metal cocatalysts and targeted quantitative macroinitiator consumption. The latter is essential to avoid tedious purification that might render the approach difficult to scale-up for applications. We further reasoned that the strong adsorption of EY on proteins<sup>73</sup> or/and its potential entrapment in the assemblies would enable direct imaging of the bioconjugates via fluorescence offering in addition one pot synthesis and labeling for studies using advanced microscopy. Following this approach we present herein, the synthesis of hydrophilic, amphiphilic, and responsive bioconjugates under mild blue light irradiation and with quantitative macroinitiator consumption attained in the presence of a tertiary amine cocatalyst.<sup>65</sup> To this end, BSA was selected as model protein since it offers valuable characteristics to biohybrid systems including lack of cytotoxicity, high stability, and ability to evade interactions with blood serum components.<sup>74</sup> Styrene, methacrylates, acrylates, and acrylamides were used as monomers. Expanding biohybrid scope to enzymes, catalytically active biohybrids were also synthesized using the lipase B from *Candida antarctica* and were imaged with fluorescence microscopy. Considering that the tertiary amines act as co-initiators,<sup>60, 75</sup> the polymerization was studied in depth revealing tandem formation of polymeric by-products. To valorize these polymers, emulsion polymerization was employed in the presence of native proteins yielding protein-coated polymer nanoparticles.

## Results and discussion

To access the oxygen tolerant, photoinduced, organocatalyzed grafting of hydrophobic polymers from ATRP protein macroinitiators we implemented an emulsion-based polymerization protocol.<sup>39</sup> EY was used as the photoredox catalyst (Figure S1) and styrene as the model monomer for the synthesis of amphiphilic bioconjugates. The use of BSA is widespread in bioconjugation studies due to its accessible free thiol enabling specific functionalization and, on this basis, it was selected as model protein. The biomacroinitiator BSA-Br ( $I_0$ ) was

synthesized following an established protocol *i.e.* Michael addition of 2-bromo-2-methyl-propionic acid (2,2,5-dioxo-2,5-dihydro-pyrrol-1-yl)-ethyl ester to the accessible cysteine residue (Cys-34) of the protein (Scheme S1, Figure S2). To evaluate the feasibility of this metal-free photoinduced approach, all reactions were studied at physiological pH (7.4), ambient temperature and under blue LED irradiation unless otherwise stated. A feed molar ratio of styrene/BSA-Br ( $I_0$ ) = 4000/1, ensuring the formation of a stable emulsion was initially evaluated in the presence of 0.02 to 1 molar equivalents of EY (Table 1, Entries 1-4) without adding either an oxygen scavenger or a sacrificial electron donor. It is important to note that all reactions were performed by simply eliminating the headspace from the reaction vessel without applying any deoxygenation<sup>76-79</sup> means and that a ventilator was used to avoid temperature increase during the reaction (near ambient temperatures varying between 25 and 35 °C were measured in the reactor). Polyacrylamide gel electrophoresis (PAGE) and aqueous Size Exclusion Chromatography (SEC) were employed to monitor the consumption of the macroinitiator and detect the formation of products. Formation of amphiphilic bioconjugates was observed for all feed molar ratios used under these conditions yet, without quantitative macroinitiator consumption (Table 1, Entries 1-3, Figure 1, Figure S3, Figure S4). A new band, not migrating past the stacking gel was observed and attributed to the amphiphilic BSA-poly(styrene) biohybrid nanoparticles which were eluted with lower retention times than the macroinitiator in aqueous SEC.<sup>35, 39</sup> All biohybrids were characterized by Infrared Spectroscopy (FT-IR, Figure S3). Lower or no macroinitiator consumption was seen when lowering the catalyst concentration to as low as 0.02 molar equivalents (Table 1, Entry 4, Figure S3, Figure S4).

Table 1. Optimization of the oxygen tolerant, photoredox grafting of styrene from BSA-Br ( $I_0$ ).

Entry	Styrene/BSA-Br, $I_0$ /EY	Reaction Time (min)	BSA-Br ( $I_0$ ) Consumption
1	4000/1/1	120	Near quantitative
2	4000/1/0.5	120	Partial
3	4000/1/0.2	120	Partial
4	4000/1/0.02	120	Low
5	4000/1/0	120	No reaction
6	4000/1/1 <sup>a</sup>	120	No reaction
7	4000/0/1	120	n.a. <sup>b</sup>
	Styrene/BSA-Br, $I_0$ /EY/AsCA	Reaction Time (min)	BSA-Br ( $I_0$ ) Consumption
8	4000/1/1/0.5	120	High
	Styrene/BSA-Br, $I_0$ /EY/TEMED	Reaction Time (min)	BSA-Br ( $I_0$ ) Consumption
9	4000/1/1/10	10-15	Quantitative
10	4000/1/0.5/5	30-45	Quantitative
11	4000/1/0.2/2	120	Near quantitative
12	4000/1/0.02/0.2	240 or 480	Low
13	4000/0/1/10	240	n.a. <sup>b</sup>
14	4000/0/0.2/2	240	n.a. <sup>b</sup>

<sup>a</sup> Without irradiation. <sup>b</sup> Formation of polystyrene nanoparticles



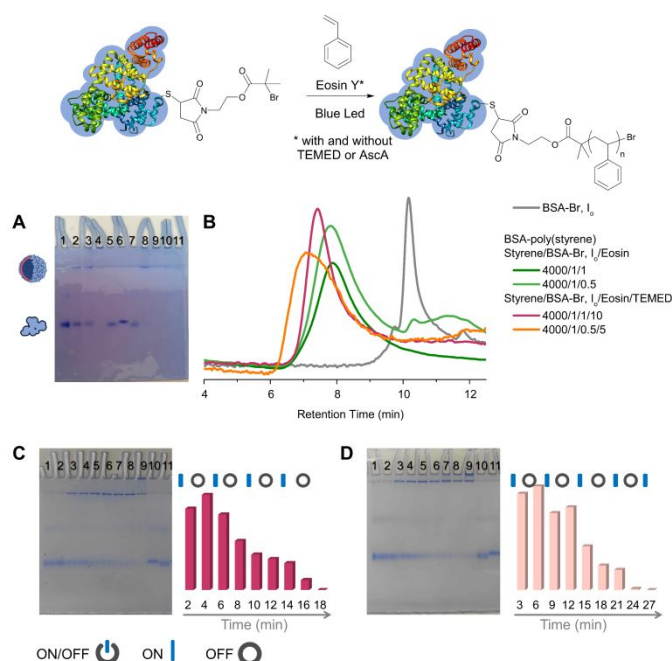


Figure 1. Synthesis of BSA-poly(styrene) via oxygen tolerant, organocatalyzed ATRP (top scheme). **A.** Native PAGE, lanes 1-4 and 7-10: BSA-poly(styrene) lane 1: Styrene/BSA-Br,  $I_0/EY=4000/1/0.02$ , lane 2: Styrene/BSA-Br,  $I_0/EY=4000/1/0.2$ , lane 3: Styrene/BSA-Br,  $I_0/EY=4000/1/0.5$ , lane 4: Styrene/BSA-Br,  $I_0/EY = 4000/1/1$ , lane 5: BSA-Br ( $I_0$ ), lane 6: native BSA, lane 7: Styrene/BSA-Br,  $I_0/EY/TEMED=4000/1/0.02/0.2$ , lane 8: Styrene/BSA-Br,  $I_0/EY/TEMED=4000/1/0.2/2$ , lane 9: Styrene/BSA-Br,  $I_0/EY/TEMED =4000/1/0.5/5$ , lane 10: Styrene/BSA-Br,  $I_0/EY/TEMED=4000/1/1/10$ , lane 11: polystyrene. **B.** SEC chromatographs of BSA-Br ( $I_0$ ) and BSA-poly(styrene) synthesized under different conditions. **C.** ON/OFF time course experiment using feed molar ratio styrene/BSA-Br,  $I_0/EY/TEMED=4000/1/1/10$ . Left: Native PAGE lanes 1-9: samples were withdrawn every 2 minutes of alternating blue LED ON and OFF periods, lane 10: native BSA, lane 11: BSA-Br ( $I_0$ ). Right: Semiquantitative analysis plot of BSA-Br ( $I_0$ ) consumption during the course of the reaction.<sup>39</sup> **D.** ON/OFF time course experiment using feed molar ratio styrene/BSA-Br,  $I_0/EY/TEMED=4000/1/0.5/5$ . Left: Native PAGE lanes 1-9: samples were withdrawn every 3 minutes of alternating blue LED ON and OFF periods, lane 10: BSA-Br ( $I_0$ ), lane 11: native BSA. Right: Semiquantitative analysis plot of BSA-Br ( $I_0$ ) consumption during the course of the reaction.<sup>39</sup>

When control experiments were performed in the absence of a selected reaction component such as the catalyst (Table 1, Entry 5), the monomer or irradiation (Table 1, Entry 6, Figure S3), no biohybrid formation could be detected while in all cases, the macroinitiator was recovered unaffected. On the other hand, polystyrene nanoparticles were formed when styrene was subjected to emulsion polymerization conditions in the absence of the protein macroinitiator BSA-Br ( $I_0$ ) (Table 1, Entry 7, Figure 2). The produced polystyrene was isolated and characterized with  $^1H$ -NMR spectroscopy (Figure S5).

Throughout this study, quantitative macroinitiator consumption was targeted as it minimizes the effort required to isolate the biohybrids by rendering only a simple dialysis step necessary. We evaluated grafting in the presence of AscA since it was elegantly employed in recent protocols as means to deoxygenate the reaction mixtures.<sup>63, 65</sup> Under the conditions used herein, grafting of styrene was found to proceed yet without quantitative macroinitiator consumption (Table 1, Entry 8, Figures S3 and S7). For this reason, we proceeded to investigate the effect of a tertiary amine sacrificial electron donor since it has previously shown in EY mediated PET RAFT

polymerizations, that the stability of the generated amine radical cation enhanced both the efficiency of the reduction of excited-state EY and oxygen tolerance.<sup>80-82</sup> Indeed, when  $N,N,N',N'$ -tetramethylethylenediamine (TEMED) was added as sacrificial electron donor,<sup>48</sup> quantitative macroinitiator consumption could be attained after merely 10 to 15 minutes of irradiation under blue LED at feed molar ratio of styrene/BSA-Br,  $I_0/EY/TEMED = 4000/1/1/10$  (Figure 1, Table 1, Entry 9, Figures S3 and S8). When reduced EY feed molar ratio was used, quantitative macroinitiator consumption could again be achieved albeit, at increased irradiation times (between 30 minutes and 2 hours depending on the photoredox catalyst loading, Table 1, Entries 10-12, Figure S8).

Imaging of the products (Table 1, Entry 9) with FE-SEM revealed two distinct populations of spherical nanoparticles with defined diameters between 100 and 130 nm and between 20 and 40 nm (Figure 2A and B). Poly(styrene) formed in the absence of macroinitiator was imaged as spherical nanoparticles with significantly smaller diameters between 10 and 40 nm (Figure 2C, Table 1, Entries 13 and 14, Figure S5). Hence, the spherical assemblies imaged in FE-SEM can be most possibly attributed to hybrid polymer/bioconjugate nanoparticles (Figure 2A and B). The nature of the nanoparticles was further elucidated through the synthesis of BSA-responsive polymer bioconjugates (vide infra). Taking into account the amphiphilicity of the bioconjugates and thus the lack of a solvent that would both dissolve them and preserve the conformation of the protein, the free polymer could not be efficiently removed from the product assemblies.

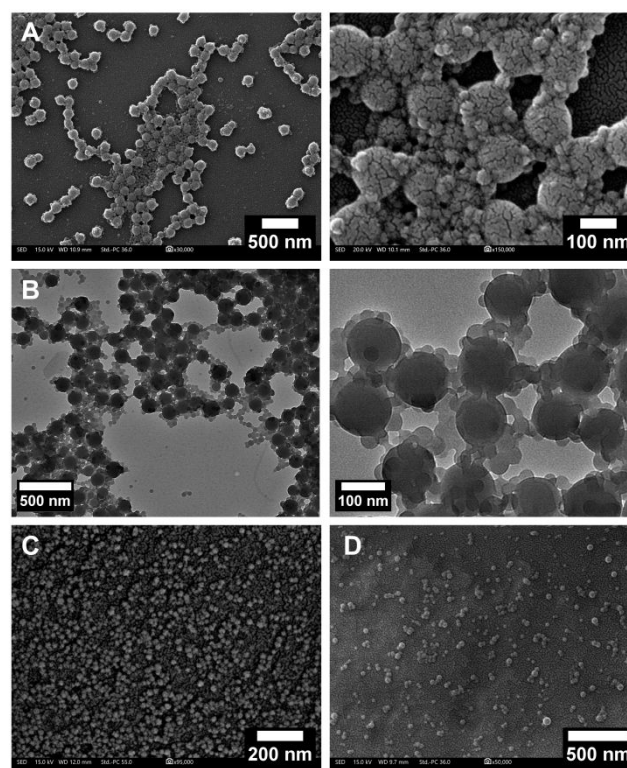


Figure 2. **A.** FE-SEM micrographs and **B.** TEM micrographs of BSA-poly(styrene) (Table 1, Entry 9) imaged as two distinct populations of spherical nanoparticles with diameters between 100 and 130 nm and between 20 and 40 nm; **C.** FE-SEM micrographs of poly(styrene) (Table 1, Entry 13) imaged as spherical nanoparticles with diameters



between 10 and 40 nm; D. FE-SEM micrographs of BSA coated poly(styrene) nanoparticles with diameters between 10 and 50 nm.

Next intermittent light exposure was investigated to assess the possibility of activating and deactivating polymerization. Rapid macroinitiator consumption was observed after 2-3 minutes irradiation time as can be observed in Figure 1C (styrene/BSA-Br,  $I_0$ /EY/TEMED = 4000/1/1/10, Table 1, Entry 9, Figure S9). This short induction period can be ascribed to the time required to *in situ* remove the oxygen from the polymerization solution and the time required for the EY radical anion to form and in turn interact with the amine co-initiator to kick-start the polymerization.<sup>83-85</sup> Under these conditions, the polymerization could be activated and deactivated by switching on and off the irradiation source until fully consuming BSA-Br (after 10 minutes of total ON irradiation time) nevertheless, temporal control was poor. We reasoned that the concentration of EY and the tertiary amine would influence both the induction period and polymerization control and therefore, to attain better temporal control, we lowered the concentration of the catalyst *i.e.*, styrene/BSA-Br,  $I_0$ /EY/TEMED = 4000/1/0.5/5 (Table 1, Entry 10, Figure 1C). The reaction could be again triggered or halted by turning the blue LEDs on and off with improved temporal control.

To further exploit this photoinduced methodology, we synthesized BSA-poly(styrene) on a larger scale using the same experimental setup. SEC chromatography verified that the macroinitiator consumption was quantitative in 6 times larger scale without the need for further optimization (Figure S9).

### Monomer Scope

To expand monomer scope, the EY mediated, photoinduced ATRP grafting of a series of acrylates, methacrylates and acrylamides from BSA-Br ( $I_0$ ) was evaluated under the oxygen

tolerant conditions established for styrene. For all hydrophobic monomers emulsion polymerization conditions were pursued *i.e.*, formation of stable monomer emulsions prior to subjecting the monomer to polymerization. As seen in Figure 3 (Table 2), hydrophobic acrylates, methacrylates and acrylamides could be successfully grafted from BSA-Br ( $I_0$ ) and for most monomers, quantitative macroinitiator consumption could be achieved through optimization of the feed molar ratio of the reactants. More specifically, the optimal feed molar ratio for the grafting of methyl acrylate (MA) was MA/BSA-Br/EY/TEMED = 4000/1/1/10, *i.e.*, same as the optimum feed ratio identified for styrene (Figures S10 and S11). In the case of methyl methacrylate (MMA), quantitative macroinitiator consumption at the same feed molar ratio could only be achieved in the presence of 5 % v/v toluene presumably stabilizing the monomer emulsion (Figures S12 and S13). In all cases the amphiphilic bioconjugates were found to assemble into hybrid polymer/biopolymer spherical nanostructures (Figure 3E).

Table 2. Oxygen tolerant, photoredox ATRP for the grafting of diverse monomers from BSA-Br ( $I_0$ ).

Entry	Monomer	Monomer/BSA-Br, $I_0$ /EY	BSA-Br ( $I_0$ ) Consumption
1	MA	4000/1/1/10	Quantitative
2	MMA	4000/1/1/10 <sup>a</sup>	Quantitative
3	VAc	8000/1/5/50	High
4	VP	4000/1/0.5/5	Quantitative
5	NAM	4000/1/1/10	Near Quantitative
6	HEA	4000/1/1/10	Quantitative
7	HEMA	4000/1/1/10	Quantitative
8	NIPAM	1000/1/1/10	Quantitative
9	NIPAM	1000/1/0.2/10	Quantitative
10	NIPAM	100/1/0.2/10	Quantitative
11	DMAEMA	4000/1/0.2/10	Quantitative
12	DPA	4000/1/0.2/10	Quantitative

<sup>a</sup> Addition of 5 % v/v toluene



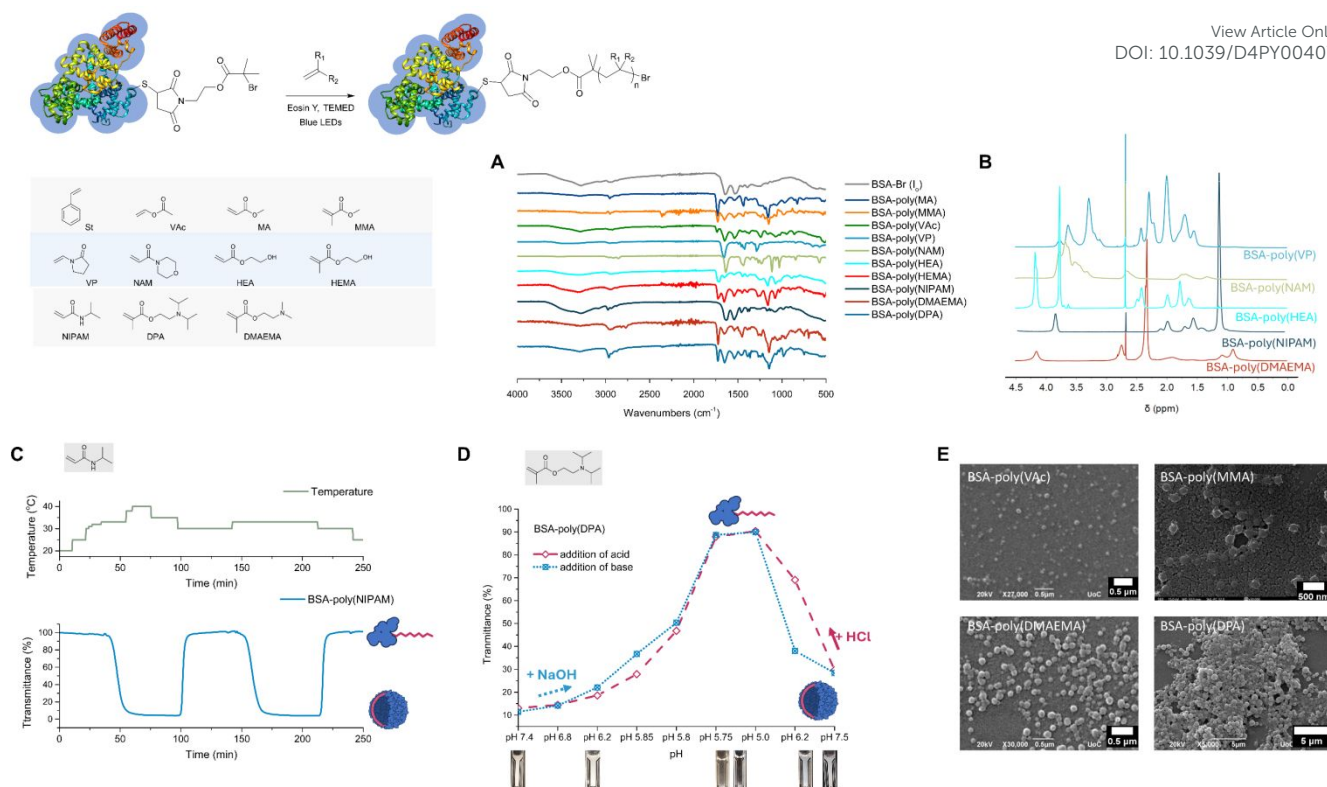


Figure 3. Characterization of amphiphilic, hydrophilic, and responsive protein-polymer conjugates. **A.** IR spectra of the bioconjugates. **B.** <sup>1</sup>H-NMR spectra acquired for hydrophilic BSA-polymer conjugates. **C.** Transmittance vs. time curve at different temperatures showing the rapid response of BSA-poly(NIPAM). **D.** Transmittance vs. pH curves of BSA-poly(DPA). Two cycles are shown for the same sample in which the response was induced by changing the pH with the addition of HCl (pH decrease) or NaOH (pH increase). **E.** SEM and FE-SEM micrographs of amphiphilic protein-polymer conjugate nanoparticles.

As seen with styrene, several other monomers used in this study (MMA, DPA and NIPAM *vide infra*) were also shown to polymerize in the absence of macroinitiator (Figure S6).

Grafting of the less activated monomer vinyl acetate (VAc) proved to be more demanding. In general, ATRP of VAc is considered highly challenging because the homolytic bond dissociation energy of the dormant poly(VAc) chains makes reactivation difficult while at the same time the VAc propagating radical is not stabilized either.<sup>86-87</sup> Indeed neither addition of an organic cosolvent nor increased catalyst loadings or grafting times could significantly increase biomacroinitiator consumption. The lowest amount of unreacted macroinitiator was detected at a feed molar ratio VAc/BSA-Br, I<sub>0</sub>/EY/TEMED = 8000/1/5/10 (Figure S14 and Figure 3E).

We also sought to graft hydrophilic monomers from BSA-Br (I<sub>0</sub>) and for this reason vinyl pyrrolidone (VP), N-acryloyl morpholine (NAM) and 2-hydroxyethyl acrylate (HEA) were selected since all produce polymers useful in a variety of pharmaceutical and biomedical applications (Figure 3).<sup>88-89</sup> <sup>1</sup>H-NMR spectroscopy provided additional means to characterize hydrophilic protein-polymer conjugates while dialysis was sufficient to remove both unreacted monomers and the produced polymers from the bioconjugate solution. It should be noted that for hydrophilic monomers, the optimum conditions of emulsion polymerization did not result in macroinitiator consumption which was more difficult to attain. Feed molar ratio VP/BSA-Br, I<sub>0</sub>/EY/TEMED = 4000/1/0.5/5 was

found sufficient to yield BSA-poly(vinyl pyrrolidone) biohybrids (Figure 3, Figure S15). For the synthesis of BSA-poly(N-acryloyl morpholine), near quantitative macroinitiator consumption was observed after optimization with NAM/BSA-Br/EY/TEMED = 4000/1/1/10, Figure 3, Figure S16). At the same molar loading both 2-hydroxyethyl acrylate (HEA) and 2-hydroxyethyl methacrylate (HEMA) led to the formation of BSA-poly(HEA) (Figure 3, Figure S187) and BSA-poly(HEMA) (Figure 3, Figure S18) respectively.

Targeting the synthesis of responsive bioconjugates, *N*-isopropylacrylamide (NIPAM), 2-(dimethylamino)ethyl methacrylate (DMAEMA) and 2-(diisopropylamino)ethyl methacrylate (DPA) were grafted from the protein macroinitiator BSA-Br (Figure 3). The conditions identified for full macroinitiator consumption are summarized in Table 2 (Figures S19-S24). To get insight on the kinetics of this oxygen-tolerant approach, the photoinduced grafting of NIPAM from BSA-Br (I<sub>0</sub>) was further studied. In time course experiments performed under the conditions identified to be optimal (NIPAM/BSA-Br, I<sub>0</sub>/EY/TEMED = 2000/1/0.2/10, Figure S19), the formation of biohybrids was apparent within the first 5 minutes of irradiation and full macroinitiator consumption could be achieved within 30 minutes. Importantly, when samples of the reaction mixture were withdrawn at fixed time points and studied with <sup>1</sup>H-NMR spectroscopy without purification, full monomer consumption was also seen after 60 minutes (Figure S19). The lower critical solution temperature (LCST) of BSA-



poly(NIPAM) was determined to be between 32.8 and 33 °C at sufficiently dilute concentrations and was found to be reversible (Figure 3, Figure S20). The spherical assemblies formed at temperatures higher than the LCST were imaged by SEM (Figure S20). The response of BSA-poly(DPA) was also found to be reversible with turning point determined to be at pH 5.8 (Figure 3, Figure S21).<sup>90</sup> Taking advantage of their response, both BSA-poly(NIPAM) and BSA-poly(DPA) could be effectively isolated from independently formed polymer chains *i.e.*, by performing dialysis after phase transition while retaining the conditions required for the biopolymer to be hydrophilic (at 20 °C for BSA-poly(NIPAM) and at pH below 5.8 for BSA-poly(DPA)). BSA-poly(DPA) was analyzed with PAGE and before and after dialysis performed at 5.5. The dialysate was collected and the released polymer isolated and characterized with <sup>1</sup>H-NMR spectroscopy (Figure S22). Similar trends were observed in the synthesis of BSA-poly(DMAEMA) (Figures S23 and S24).

### Grafting multiple monomers

To capitalize on the unlimited chemical versatility of polymers we investigated the possibility to graft two different monomers from the protein initiator via this oxygen tolerant, metal-free, photocatalysis. A random BSA-poly(NIPAM-co-DPA) was synthesized by grafting both monomers together (Figure S25). To explore the livingness of this approach, we then proceeded to consecutively graft two different monomers. To achieve this, full consumption of both the macroinitiator and the monomer were targeted for the first step. Quantitative consumption of the macroinitiator was confirmed by PAGE electrophoresis, and full monomer consumption was confirmed by <sup>1</sup>H-NMR spectroscopy for the synthesis of BSA-poly(NIPAM) at feed molar ratio NIPAM/BSA-Br, I<sub>0</sub>/EY/TEMED = 100/1/0.2/10. After the first monomer, NIPAM, was fully consumed, styrene, EY and TEMED were added to the reaction mixture (styrene/BSA-Br, I<sub>0</sub>/EY/TEMED = 4000/1/0.2/10) and the reaction was allowed to proceed for another hour under blue LED. The formation of BSA-poly(NIPAM)-b-poly(styrene) was verified through the FT-IR spectrum of the biohybrid exhibiting all the characteristic vibrations of the protein and both polymer moieties (Figure S26). Under the same conditions, the responsive BSA-poly(NIPAM)-b-poly(VP) was also synthesized (Figure S27).

### Protein-coated polymer nanoparticles

An underlying goal of this study was to develop a facile, easy to implement and rapid protocol which would allow to easily tailor hybrid nanocarriers for diverse imaging applications given that EY strongly attaches to proteins. Key element to the implementation of such nanocarriers as drug or signal delivery systems is to attain mechanistic insights on internalization pathways and membrane/organelle interactions using fluorescent microscopy.<sup>91-93</sup> Since several of the monomers used in this study polymerize under the conditions of this oxygen tolerant photoinduced polymerization to form polymer nanoparticles (*vide supra*), we envisioned that this approach could be used to construct protein-coated polymer nanoparticles. We reasoned that during emulsion

polymerization, a native protein could act as surfactant further stabilizing the monomer emulsion. In such a case, protein-coated nanoparticles would be formed during EY mediated photopolymerization of styrene and stabilized through hydrophobic interactions.

We therefore performed styrene polymerization in the presence of native BSA without adding the ATRP initiator BSA-Br, I<sub>0</sub>. In PAGE electrophoresis, a band not-migrating past the stacking gel front, was predominant upon completion of the reaction while native BSA could also be detected (Figure S28). After the dialysis step, the presence of both BSA and poly(styrene) was confirmed in the product mixture with FT-IR. The nanoparticles were visualized via FE-SEM imaging to be spherical with diameters varying between 10 and 50 nm (Figure 2D). Despite numerous efforts, the protein could not be fully detached from the nanoparticles by simple means that would allow further characterization post polymerization. We therefore proceeded to synthesize responsive poly(DPA) nanoparticles in the presence of native BSA (Figure 4, Figure S23). To determine the nature of the produced nanoparticles, the product was characterized after synthesis and was then subjected to dialysis against phosphate buffer, pH 5.0 *i.e.*, below the turning point (5.8, Figure 3). Both the product and the dialysate were characterized. As seen in native PAGE analyses of the samples collected before and after the phase transition, native BSA (pI 4.8-5.0) was liberated leaving no trace of the band attributed to the nanocarrier (Figure S22). Our initial assumption was further supported through the detection of poly(DPA) obtained by acquiring a <sup>1</sup>H-NMR spectrum of the dialysate (Figure S22).

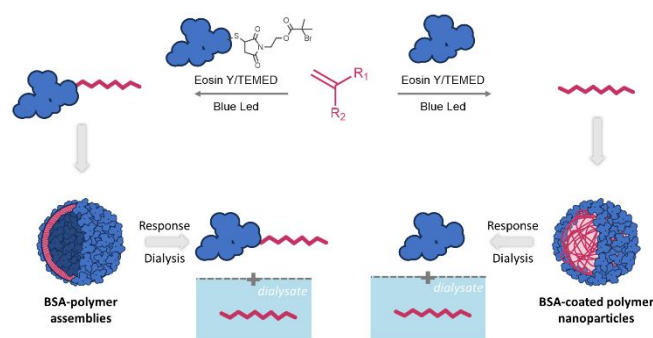


Figure 4. Proposed pathways to produce BSA-polymer and BSA-coated polymer nanoparticles.

### Imaging with fluorescence microscopy

EY has an emission peak at 516.5 nm and is detectable in fluorescence microscopy. As previously reported, EY strongly attaches to proteins which could be advantageous for the purposes of biomedical research imaging since EY is biocompatible and non-toxic. The protein-coated poly(styrene) nanoparticles were imaged with total internal reflection fluorescence (TIRF) microscopy and detected in the green channel (Figure 5, Figures S28 and S29).





### Protein scope – Synthesis of CALB-poly(styrene)

To further explore the versatility of this oxygen tolerant photoinduced organocatalysis, the lipase B from *Candida antarctica* (CALB) was employed. To synthesize a CALB initiator, N-hydroxysuccinimide-2-bromo-2-methylpropionate was non-specifically linked via NHS-ester coupling to the exposed primary amines of the protein (Figure S30). Upon isolating and characterizing the macroinitiator, the grafting of styrene was endeavored at feed molar ratio styrene/CALB-Br, I<sub>0</sub>/EY/TEMED = 4000/1/1/10. The formation of CALB-poly(styrene) was verified via SDS PAGE and FT-IR (Figure S31). More specifically, a new non-migrating band was observed for the product in SDS PAGE which was pleasingly combined with the absence of the band corresponding to the macroinitiator. Consistent with what was seen with BSA, two populations of assembled nanoparticles were imaged in SEM with the ones which were larger in diameter (100-150 nm) having spherical and distorted spherical architectures (Figure S32). The FT-IR spectrum of the product verified the presence of all the characteristic vibrations of CALB-Br and poly(styrene) (Figure S31).

CALB catalyzes the hydrolysis of esters converting triglycerides into glycerol and fatty acids, while being also one of the most used enzymes in biocatalysis with widespread applications.<sup>94</sup> 5-(6)-carboxyfluorescein diacetate (CFDA) was used to test *in vitro* the catalytic activity of the CALB-poly(styrene) biohybrids by monitoring the formation of the hydrolysis product carboxyl fluorescein (CF) at 453 nm. The biohybrids were shown to retain part of the catalytic activity of the parent enzyme.

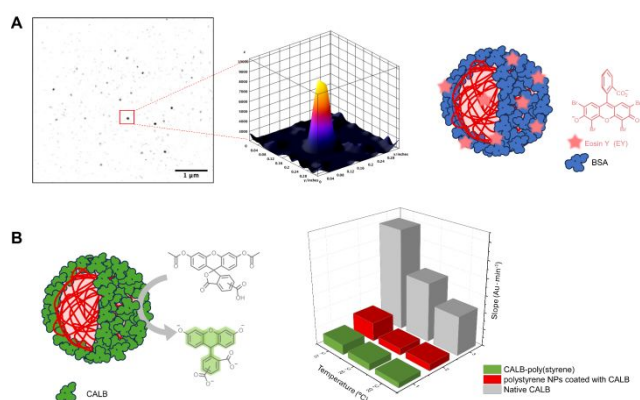


Figure 5. **A.** Left: Imaging of BSA coated poly(styrene) with internal reflection fluorescence (TIRF) microscopy. Right: 3D intensity plot of one nanoparticle. **B.** Activity of CALB-poly(styrene), polystyrene nanoparticles coated with CALB and native CALB. The graph depicts the slopes of the activity kinetics recorded in 20, 25 and 37 °C.

### CALB-coated polystyrene nanoparticles

Poly(styrene) nanoparticles were synthesized in the presence of native CALB (1 equiv.) using feed molar ratio styrene/EY/TEMED = 4000/1/10 under blue LED for one hour. The nanoparticles were imaged with FE-SEM while the product was characterized with PAGE electrophoresis and FT-IR (Figure S5).

The CALB-coated polystyrene nanoparticles were also found to retain part of the esterase activity of native CALB (Figure 5). Notably, the coated nanoparticles were proven to be

remarkably stable as they retained their activity one year after storing at 4 °C (Figure S33, activity data not shown). To the best of our knowledge this is the first time that such significant stability of such nanocarriers is being reported.

## Experimental

### Materials and methods

Chemicals were purchased from commercial sources and were used as received, unless otherwise stated. Bovine serum albumin (BSA) was purchased from Sigma (> 99%). The purification of CALB was performed according to literature.<sup>95</sup> Dialysis bags (Spectra/Por® Biotech Regenerated Cellulose Dialysis Membranes, MWCO 10, 25, and 50 kDa) were purchased from Spectrum Labs. The synthesis of the biomacroinitiators was performed using established protocols.<sup>35, 39</sup> Full experimental details and characterization are included in the Supplementary information.

### General Polymerization protocol for the oxygen tolerant, EY/TEMED mediated grafting of monomers from protein macroinitiators

A solution of EY was prepared by dissolving 1 mg EY (1.54 μmol) in 1 mL, 20 mM phosphate buffer pH 7.4 with the aid of sonication. 0.21 M and 0.1 M TEMED stock solutions were prepared by dissolving 3.3 μL (22 μmol) in 100 μL nanopure water or 1.5 μL (10 μmol) in 98.5 μL nanopure water. 2.8 μL - 141.5 μL (0.044-0.218 μmol) of the stock solution of EY and the corresponding volume of the appropriate TEMED stock solution were dissolved in nanopure water to afford a solution with fixed total volume (460 μL). The emulsion of the monomer was formed by adding the hydrophobic monomer (872 μmol, 4000 equiv.) and sonicating for ca. 5 minutes. The volume of the water was adjusted for each feed molar ratio to retain a stable volume. The resulting emulsion was immediately transferred to a 6 mL polypropylene syringe equipped with a stirring bar, containing 0.625 mL of a 0.35 mM solution of the protein macroinitiator (I<sub>0</sub>) in 20 mM phosphate buffer, pH 7.4 (0.218 μmol, 1 equiv.). Headspace was eliminated to avoid the presence of undissolved oxygen and the reaction syringe was capped and placed under blue LED irradiation for specified amounts of time (varying from 5 minutes to 9 hours) with moderate stirring. A ventilator was used to avoid temperature increase maintaining the temperature between 25 and 35 °C. The reaction mixture was then dialyzed using a 10 kDa MWCO regenerated cellulose dialysis membrane initially against a mixture of 5 mM phosphate buffer, pH 7.4, 1 % DMSO, then against 5 mM phosphate buffer, pH 7.4, and finally against 20 mM phosphate buffer, pH 7.4. The product solutions were analyzed by means of native or SDS PAGE electrophoresis, SEC, and FT-IR spectroscopy. <sup>1</sup>H-NMR spectra were acquired for hydrophilic products. Dilute suspensions of the products in nanopure water were imaged with SEM or FE-SEM. All products were stored at 7 °C until further use.



## Conclusions

A comparative study of a robust EY/TEMED photocatalyzed, oxygen tolerant protocol that enables the synthesis of protein-polymer conjugates is presented. For the purposes of this study, we optimized photocatalysis and used it as a rapid and easy to implement protocol to graft diverse monomers from a protein macroinitiator while targeting at complete macroinitiator consumption in order to attain at the same time easy isolation means. In this manner, amphiphilic, hydrophilic and responsive bioconjugates were synthesized and characterized. The photoinduced EY/TEMED mediated grafting was found to be easily scalable. Expanding the scope of this protocol, triblock biohybrids could also be easily obtained. The EY mediated oxygen tolerant ATRP was also successfully applied to CALB, yielding biohybrids that retained part of the parent enzyme activity. Taking advantage of the ability of EY/TEMED to mediate vinyl monomer polymerization in emulsion, we studied the *in situ* formation and protein-coating of polymer nanoparticles. Both BSA and CALB were used to coat poly(styrene) and poly(DPA) nanoparticles. Interestingly, the CALB-coated poly(styrene) nanoparticles were found to be active after being stored for over a year at 4 °C. Nanoparticle protein coronas are spontaneously formed when they enter biological systems as part of their defence mechanisms. Our current studies are focusing on this extremely interesting feature of the EY mediated approach which provides the means to synthesize polymer nanoparticles coated with a defined protein corona to explore whether this can in turn dictate the biophysical and chemical identity of the nanoparticle.

## Author Contributions

E.V., Th.L., J.B., S.M., M. Ch., K.V. contributed to the investigation and data curation. S.M.C., N.S.H., K.V. supervision and resources. K.V. conceptualization and methodology. E.V. and Th.L. writing of the original draft. K.V. writing, review & editing. The final manuscript was reviewed by all authors.

## Conflicts of interest

Sune M. Christensen is employed by Novonosis.

## Data availability

The data supporting this article have been included as part of the Supplementary Information.

## Acknowledgements

We acknowledge Jeannette de Sparra Lundin, Gustav Hammerich Hansen and Christian Isak Jørgensen for assisting with CalB expression, purification, and characterization. The authors acknowledge the General Secretariat for Research and Technology (GSRT) - Hellenic Foundation for Research and Innovation (HFRI) ΕΛΙΔΕΚ program (11118) for funding. The

authors acknowledge funding from The Independent Research Fund Denmark (1127-00432B) Villum foundation (40801) and the NNF challenge center for Optimised Oligo Escape and control of disease (NNF23OC0081287).

## Notes and references

- R. A. Olson, A. B. Korpusik and B. S. Sumerlin, *Chem. Sci.*, 2020, **11**, 5142.
- M. S. Messina, K. M. Messina, A. Bhattacharya, H. R. Montgomery and H. D. Maynard, *Prog. Polymer Sci.*, 2020, **100**, 101186.
- A. J. Russell, S. L. Baker, C. M. Colina, C. A. Figg, J. L. Kaar, K. Matyjaszewski, A. Simakova and B. S. Sumerlin, *AIChE J.*, 2018, **64**, 3230.
- S. C. Tam, J. Blumenstein and K. Wong, *Proc. Natl Acad. Sci. USA*, 1976, **73**, 2128.
- A. Abuchowski, T. Van, Es, N. C. Palczuk, and F. F. Davis, *J. Biol. Chem.*, 1977, **252**, 3578.
- F. M. Veronese, R. Largajolli, E. Boccù, C.A. Benassi and O. Schiavon, *Appl. Biochem. Biotechnol.*, 1985, **11**, 141.
- J. M. Harris and R. B. Chess, *Nat. Rev. Drug Discovery*, 2003, **2**, 214.
- E. M. Pelegri-O'Day, E. W. Lin and H. D. Maynard, *J. Am. Chem. Soc.*, 2014, **136**, 14323.
- S. N. Alconcel, A. S. Baas and H. D. Maynard, *Polym. Chem.*, 2011, **2**, 1442.
- A. M. Ramos-de-la-Peña and O. Aguilar, *Int. J. Pept. Res. Ther.*, 2019, **26**, 333.
- C. A. Stevens, K. Kaur and H.-A. Klok, *Adv. Drug Deliv. Rev.*, 2021, **174**, 447.
- P. Kiran, A. Khan, S. Neekhra, S. Pallod, and R. Srivastava, *Front. Med. Technol.* 2021, **3**, 676025.
- S. Bhattacharjee, W. G. Liu, W. H. Wang, I. Weitzhandler, X. H. Li, Y. Z. Qi, J. Y. Liu, Y. Pang, D. F. Hunt and A. Chilkoti, *Chembiochem*, 2015, **16**, 2451.
- A. S. Hoffman, *Adv. Drug. Deliv. Rev.*, 2013, **65**, 10.
- Z. Liu, C. Dong, X. Wang X, H. Wang, W. Li, J. Tan and J. Chang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 2393.
- F. Duan, W. Jin, T. Zhang, Y. Sun, X. Deng, W. Gao, *Adv. Mater.*, 2023, 2209765.
- X. Huang, M. Li, D. Green, D. S. Williams, A. J. Patil and S. Mann, *Nat. Commun.*, 2013 **4**, 2239.
- J. M. Hoffman, P. S. Stayton, A. S. Hoffman and J. J. Lai, *Bioconjugate Chem.*, 2015, **26**, 29-38.
- K. Velonia, A. E. Rowan and R. J. M. Nolte, *J. Am. Chem. Soc.*, 2002, **124**, 4224.
- M. J. Boerakker, J. M. Hannink, P. H. H. Bomans, P. M. Frederik, R. J. M. Nolte, E. M. Meijer and N. A. J. M. Sommerdijk, *Angew. Chem. Int. Ed.*, 2002, **41**, 4239.
- C. Bao, Y. Yin and Q. Zhang, *Biomacromolecules*, 2018, **19**, 1539; C. Y. Bao and Q. Zhang, *Eur. Polym. J.*, 2019, **112**, 263-272; C. W. Chiang, X. Liu, J. Sun, J. Guo, L. Tao and W. Gao, *Nano Lett.*, 2020, **20**, 1383.
- G. Mantovani, F. Locolley, L. Tao, D. M. Haddleton, C. Clerx, J. J. L. M. Cornelissen and K. Velonia, *J. Am. Chem. Soc.*, 2005, **127**, 2966.
- Y. Wang, and C. Wu, *Biomacromolecules*, 2018, **19**, 1804.
- K. Velonia, *Polym. Chem.*, 2010, **1**, 944.
- C. A. Lackey, N. Murthy, O. W. Press, D. A. Tirrell, A. S. Hoffman and P. S. Stayton, *Bioconjugate Chem.*, 1999, **10**, 401.
- S. Kulkarni, C. Schilli, A. Müller, A. Hoffman and P. Stayton, *Bioconjugate Chem.*, 2004, **15**, 747.
- X. Wan, G. Zhang, Z. Ge, R. Narain and S. Liu, *Chem. - Asian J.* 2011, **6**, 2835.



- 28 K. Parkatzidis, H. S. Wang, N. P. Truong and A. Anastasaki *Chem.*, 2020, **7**, 1575.
- 29 R. A. Olson, A. B. Korpusik and B. S. Sumerlin, *Chem. Sci.*, 2020, **11**, 5142.
- 30 B. Kaupbayeva and A. J. Russell, *Prog. Polym. Sci.*, 2020, **101**, 101194.
- 31 X. Liu and W. Gao, *Angew. Chem., Int. Ed.*, 2021, **60**, 2.
- 32 M. Heredero and A. Beloqui, *ChemBioChem.*, 2023, **24**, e202200611.
- 33 M. J. Tamasi, R. A. Patel, C. H. Borca, S. Kosuri, H. Mugnier, R. Upadhyaya, N. S. Murthy, M. A. Webb and A. J. Gormley, *Adv. Mater.*, 2022, **34**, 2201809.
- 34 K. L. Heredia, D. Bontempo, T. Ly, J. T. Byers, S. Halstenberg and H. D. Maynard, *J. Am. Chem. Soc.*, 2005, **127**, 16955.
- 35 B. Le Droumaguet and K. Velonia, *Angew. Chem., Int. Ed.*, 2008, **47**, 6263.
- 36 H. Murata, C. S. Cummings, R. R. Koepsel and A. J. Russell, *Biomacromolecules*, 2014, **15**, 2817.
- 37 D. Cohen-Karni, M. Kovaliov, T. Ramelot, D. Konkolewicz, S. Graner and S. Averick, *Polym. Chem.*, 2017, **8**, 3992.
- 38 C. Bao, J. Chen, D. Li, A. Zhang and Q. Zhang, *Polym. Chem.*, 2020, **11**, 1386.
- 39 A. Theodorou, E. Liarou, D. M. Haddleton, I. G. Stavarakaki, P. Skordalidis, R. Whitfield, A. Anastasaki and K. Velonia, *Nat. Commun.*, 2020, **11**, 1486.
- 40 A. Theodorou, D. Gounaris, E. Voutyritsa, N. Andrikopoulos, C. I. M. Baltzaki, A. Anastasaki, K. Velonia, *Biomacromolecules*, 2022, **23**, 4241.
- 41 E. Voutyritsa, C. Gryparis, A. Theodorou, and K. Velonia, *Macromol. Rapid Commun.* 2023, 2200976
- 42 Q. Zhang, M. Li, C. Zhu, G. Nurumbetov, Z. Li, P. Wilson, K. Kempe and D. M. Haddleton, *J. Am. Chem. Soc.*, 2015, **137**, 9344.
- 43 Y. Liu, T. K. Nevanen, A. Paananen, K. Kempe, P. Wilson, L. S. Johansson, J. J. Joensuu, M. B. Linder, D. M. Haddleton and R. Milani, *ACS Appl Mater Interfaces*, 2019, **11**, 3599.
- 44 J. Lu, H. Wang, Z. Tian, Y. Hou and H. Lu, *J. Am. Chem. Soc.*, 2020, **142**, 1217.
- 45 C. Bao, X. Xu, J. Chen and Q. Zhang, *Polym. Chem.*, 2020, **11**, 682.
- 46 J. Liu, V. Bulmus, D. L. Herlambang, C. Barner-Kowollik, M. H. Stenzel and T. P. Davis, *Angew. Chem., Int. Ed.*, 2007, **46**, 3099.
- 47 J. Xu, K. Jung, N. A. Corrigan and C. Boyer, *Chem. Sci.*, 2014, **5**, 3568.
- 48 M. Kovaliov, M. L. Allegranza, B. Richter, D. Konkolewicz and S. Averick, *Polymer*, 2018, **137**, 338.
- 49 A. E. Enciso, L. Fu, A. J. Russell and K. Matyjaszewski, *Angew. Chem., Int. Ed.*, 2018, **57**, 933.
- 50 J. Yeow, R. Chapman, A. J. Gormley and C. Boyer, *Chem. Soc. Rev.*, 2018, **47**, 4357.
- 51 L. Fu, Z. Wang, S. Lathwal, A. E. Enciso, A. Simakova, S. R. Das, A. J. Russell and K. Matyjaszewski, *ACS Macro Lett.*, 2018, **7**, 1248.
- 52 Y. Sun, S. Lathwal, Y. Wang, L. Fu, M. Olszewski, M. Fantin, A. E. Enciso, G. Szczepaniak, S. Das and K. Matyjaszewski, *ACS Macro Lett.*, 2019, **8**, 603.
- 53 A. Theodorou, P. Mandriotis, A. Anastasaki and K. Velonia, *Polym. Chem.*, 2021, **12**, 2228.
- 54 X. Pan, M. Fantin, F. Yuan and K. Matyjaszewski, *Chem. Soc. Rev.*, 2018, **47**, 5457.
- 55 A. Anastasaki, V. Nikolaou, Q. Zhang, J. Burns, S. R. Samanta, C. Waldron, A. J. Haddleton, R. McHale, D. Fox, V. Percec, P. Wilson and D. M. Haddleton, *J. Am. Chem. Soc.*, 2014, **136**, 1141.
- 56 N. D. Dolinski, Z. A. Page, E. H. Discekici, D. Meis, I. H. Lee, G. R. Jones, R. Whitfield, X. Pan, B. G. McCarthy, S. Shanmugam, V. Kottisch, B. P. Fors, C. Boyer, G. M. Miyake, K. Matyjaszewski, D. M. Haddleton, J. R. de Alaniz, A. Anastasaki and C. J. Hawker, *J. Polym. Sci. Part A*, 2019, **57**, 2688.
- 57 S. Dadashi-Silab, I. -H. Lee, A. Anastasaki, F. Lorandi, B. Narupai, N. D. Dolinski, M. L. Allegranza, M. Fantin, D. Konkolewicz, C. J. Hawker and K. Matyjaszewski, *Macromolecules*, 2020, **53**, 5280.
- 58 D. A. Corbin and G. M. Miyake, *Chem. Rev.*, 2022, **122**, 1830.
- 59 C. Kutahya, F. S. Aykac, G. Yilmaz and Y. Yagci, *Polym. Chem.*, 2016, **7**, 6094.
- 60 G. Yilmaz and Y. Yagci, *Polym. Chem.*, 2018, **9**, 1757.
- 61 S. de Avila Goncalves, P. R. Rodrigues and R. Pioli Vieira, *Macromol. Rapid Commun.*, 2021, **42**, e2100221.
- 62 B. S. Tucker, M. L. Coughlin, C. A. Figg and B. S. Sumerlin, *ACS Macro Lett.*, 2017, **6**, 452.
- 63 R. A. Olson, J. S. Levi, G. M. Scheutz, J. J. Lessard, C. A. Figg, M. N. Kamat, K. B. Basso, and B. S. Sumerlin, *Macromolecules*, 2021, **54**, 4880.
- 64 K. Kapil, A. M. Jazani, G. Szczepaniak, H. Murata, M. Olszewski and K. Matyjaszewski, *Macromolecules*, 2023, **56**, 2017.
- 65 T. Zhang, Z. Wu, G. Ng and C. A. Boyer, *Angew. Chem., Int. Ed.*, 2023, e202309582.
- 66 C. Kutahya, F. C. Aykac, G. Yilmaz, and Y. Yagci, *Polym. Chem.*, 2016, **7**, 6094.
- 67 K. Parkatzidis, N. P. Truong, M. N. Antonopoulou, R. Whitfield, D. Konkolewicz and A. Anastasaki, *Polym. Chem.*, 2020, **11**, 4968.
- 68 V. Bellotti, K. Parkatzidis, H. S. Wang, N. D. A. Watuthanthrige, M. Orfano, A. Monguzzi, N. P. Truong, R. Simonutti, and A. Anastasaki, *Polym. Chem.*, 2023, **14**, 253.
- 69 V. Srivastava and P. P. Singh, *RSC Adv.*, 2017, **7**, 31377.
- 70 S. Shanmugam, S. Xu, N. N. M. Adnan and C. Boyer, *Macromolecules*, 2018, **51**, 779.
- 71 G. Szczepaniak, J. Jeong, K. Kapil, S. Dadashi-Silab, S. S. Yerneni, P. Ratajczyk, S. Lathwal, D. J. Schild, S. R. Das and K. Matyjaszewski, *Chem. Sci.*, 2022, **13**, 11540.
- 72 K. Kapil, G. Szczepaniak, M. R. Martinez, H. Murata, A. M. Jazani, J. Jeong, S. R. Das and K. Matyjaszewski, *Angew. Chem., Int. Ed.*, 2023, e202217658.
- 73 A. Cvetkovic, A. J. J. Straathof, R. Krishna and L. A. M. van der Wielen, *Langmuir*, 2005, **21**, 1475.
- 74 J. Mariam, S. Sivakami and P. M. Dongre, *Drug Deliv.*, 2016, **23**, 2668.
- 75 J.-P. Fouassier, F. Morlet-Savary, J. Laleve'e, X. Allonas and C. Ley, *Materials*, 2010, **3**, 5130.
- 76 E. Liarou, R. Whitfield, A. Anastasaki, N. G. Engelis, G. R. Jones, K. Velonia and D. M. Haddleton, *Angew. Chem. Int. Ed.*, 2018, **57**, 8998.
- 77 E. Liarou, A. Anastasaki, R. Whitfield, C. E. Iacono, G. Patias, N. G. Engelis, A. Marathianos, G. R. Jones and D. M. Haddleton, *Polym. Chem.*, 2019, **10**, 963.
- 78 E. Liarou, Y. Han, A. M. Sanche, M. Walker and D. M. Haddleton, *Chem. Sci.*, 2020, **11**, 5257.
- 79 N. A. Swisher, D. A. Corbin and G. M. Miyake, *ACS Macro Lett.*, 2021, **10**, 453.
- 80 Y. Lee, C. Boyer and M. S. Kwon, *Chem. Soc. Rev.*, 2023, **52**, 3035.
- 81 B. Nomeir, O. Fabre and K. Ferji, *Macromolecules* 2019, **52**, 6898.
- 82 Z. Liang, S. Xu, W. Tian and R. Zhang, *Beilstein J. Org. Chem.* 2015, **11**, 425.
- 83 B. Cornils, W. A. Herrmann, J.-H. Xu and H. -W. Zanthoff, *Catalysis from A to Z: a concise encyclopedia*. 2020, Weinheim: John Wiley and Sons; 10.1002/9783527809080
- 84 N. El Achi, Y. Bakkour, W. Adhami, J. Molina, M. Penhoat, N. Azaroual, L. Chausset-Boissarie and C. Rolando, *Front. Chem.*, 2020, **8**, 740.



## ARTICLE

Journal Name

- 85 D. Bondarev, K. Borská, M. Šoral, D. Moravčíková and J. Mosnáček, *Polymer*, 2019, **161**, 122.
- 86 F. Lorandi and K. Matyjaszewski, *Isr. J. Chem.*, 2020, **60**, 108.
- 87 P. G. Falireas, V. Ladmiraal, A. Debuigne, C. Detrembleur, R. Poli and B. Ameduri, *Macromolecules*, 2019, **52**, 1266.
- 88 M. Teodorescu and M. Bercea, *Polym. Plast. Technol. Eng.*, 2015, **54**, 923.
- 89 A. Oucif, N. Haddadine, D. Zakia, N. Bouslah, A. Benaboura, K. Beyaz, B. Guedouar and M. S. El-Shall, *Polym. Bull.*, 2022, **79**, 153.
- 90 L. Papadimitriou, A. Theodorou, M. Papageorgiou, E. Voutyritsa, A. Papagiannaki, K. Velonia and A. Ranella, *J. Drug. Deliv. Sci. Technol.*, 2022, **75**, 103591.
- 91 H. D. Pinholt, S. S.-R. Bohr, J. F. Iversen, W. Boomsma and N. S. Hatzakis, *Proc. Natl. Acad. Sci. U.S.A.*, 2021, **31**, 118.
- 92 S. S.-R. Bohr, P. M. Lund, A. S. Kallenbach, H. Pinholt, J. Thomsen, L. Iversen, A. Svendsen, S. M. Christensen and N. S. Hatzakis, *Sci. Rep.*, 2019, **9**, 2654.
- 93 H. Zhao, E. Ibarboure, V. Ibrahimova, Y. Xiao, E. Garanger and S. Lecommandoux, *Adv. Sci.*, 2021, **8**, 2102508.
- 94 F. Akram, A. S. Mir, A.S., I. ul Haq and A. Roohi, *Mol. Biotechnol.*, 2023, **65**, 521.
- 95 M. Skjøt, L. De Maria, R. Chatterjee, A. Svendsen, S. A. Patkar, P. Østergaard and J. B. Dret, *ChemBioChem*, 2009, **10**, 520.

View Article Online  
DOI: 10.1039/D4PY00407H

Open Access Article. Published on 10 2024. Downloaded on 17/07/24 9:20:38.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Polymer Chemistry Accepted Manuscript