


Cite this: *RSC Adv.*, 2025, 15, 23643

Facile synthesis of Fe₃O₄@pyrogallol-formaldehyde resin@Ag core–shell nanomaterials for the catalytic degradation of contaminants

Liping Jiang, Yang Xi, Ziyi Xu, Zewen Song, Yuwei Cui and Haijun Zhou *

Noble metal nanoparticles (NPs) show excellent performance in catalysis, but their strong aggregation effect can lead to a decrease in or even disappearance of their catalytic activity. In this study, Fe₃O₄@pyrogallol-formaldehyde resin@Ag (Fe₃O₄@PGFR@Ag) nanomaterials were synthesized using Fe₃O₄ as a magnetic core and pyrogallol-formaldehyde resin (PGFR) as a shell layer. The presence of Fe₃O₄ ensured rapid material recovery. At the same time, the phenolic hydroxyl group in PGFR enabled the *in situ* reduction of Ag⁺ to form embedded Ag NPs, effectively avoiding the aggregation and shedding of Ag NPs. Cetyltrimethylammonium bromide (CTAB) was used to modify the surface charge of the catalyst. Results showed that negatively charged Fe₃O₄@PGFR@Ag exhibited high catalytic activity, with a 90% higher catalytic rate constant for cationic dye rhodamine B (RhB) compared with Fe₃O₄@PGFR@Ag-CTAB. Positively charged Fe₃O₄@PGFR@Ag-CTAB showed high catalytic activity, with a 124% higher catalytic rate constant for the anionic dye methyl orange (MO) compared with Fe₃O₄@PGFR@Ag. Therefore, the matching of the charges of the catalyst and contaminants, which facilitates the adsorption of the pollutants around the catalyst, has a significant impact on the catalytic performance and should be considered in the process of pollutant treatment.

Received 20th April 2025

Accepted 19th June 2025

DOI: 10.1039/d5ra02755a

rsc.li/rsc-advances

1. Introduction

The rapid development of modern industries has brought great convenience to humanity, but it has resulted in serious water pollution.^{1–3} Many organic dyes exhibiting persistent biotoxicity are difficult to degrade and enter the natural water circulation system *via* industrial wastewater, posing a significant threat to human survival and the sustainable and healthy development of the natural environment.^{4–7} Anionic dyes such as methyl orange (MO), which is widely used in leather and wool production; rhodamine B (RhB), used in the cosmetics industry; and tetracycline (TC), used in the medical sector, can pose a serious threat to the health of the natural environment and the survival of flora and fauna if improperly treated.^{8,9} Therefore, organic dye removal and rapid decolorization have become important research topics. Noble metal nanoparticles have been identified as an effective means to achieve this goal and have attracted much attention in the past few decades.^{10–13}

According to reports, noble metal nanoparticles have good catalytic selectivity for organic pollutants and have attracted extensive attention from researchers in the past few decades.^{14–16} Ag nanoparticles (NPs) can quickly realize electron transfer in a catalytic system, accelerating the catalytic

hydrogenation process on the surface of organic pollutants, ultimately leading to the decolorization of organic pollutants such as RhB and MO.^{17–20} However, the strong aggregation tendency of Ag nanoparticles makes them easily agglomerate, resulting in a decrease in or even disappearance of their catalytic activity.^{21–28} Moreover, individual nanoparticles are difficult to separate from the catalytic system, making it impossible to achieve controlled recycling of the catalytic material. Therefore, magnetic core–shell materials that can be quickly recycled and stably loaded onto noble metal nanoparticles have attracted researchers' attention.^{29–35}

In this study, we designed Fe₃O₄@PGFR@Ag nanomaterials, which are composed of magnetic Fe₃O₄ as a core material and pyrogallol-formaldehyde resin (PGFR) as a shell material. The presence of magnetic core materials ensures the rapid recovery of nanoparticles after catalysis. PGFR possesses strong adhesion and easy surface modification properties. During the reduction of AgNO₃, the phenolic hydroxyl groups on the surface of PGFR enable the *in situ* reduction of AgNO₃ without external reducing agents. By contrast, in silicon-based material systems, the reduction of AgNO₃ requires the addition of external reducing agents, such as hydrazine hydrate. Fe₃O₄@PGFR@Ag exhibits excellent catalytic activity for the cationic dye RhB. Therefore, nanomaterials whose surface charges are switched using CTAB exhibit efficient catalytic activity toward anionic dyes.

School of Materials Science and Engineering, Jiangsu University of Science and Technology, Zhenjiang, China. E-mail: zhouhaijun@just.edu.cn



2. Experimental section

2.1 Materials and chemicals

Iron(III) chloride hexahydrate ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$), trisodium citrate dihydrate, ethylene glycol, anhydrous sodium acetate, pyrogallol, a formaldehyde solution (37–40%), an ammonium solution (25–28%), silver nitrate, sodium borohydride (NaBH_4), cetyltrimethylammonium bromide, rhodamine B (RhB), tetracycline (TC), and methyl orange (MO) were purchased from Sinopharm Chemical Reagent Co., Ltd. All chemicals were used as received.

2.2 Synthesis of Fe_3O_4

The synthesis of Fe_3O_4 nanoparticles was performed using the following procedure.³⁶ Briefly, 1.08 g of $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ and 0.46 g of trisodium citrate were added to 40 mL of ethylene glycol to form a dispersed solution by stirring at room temperature. Then, 2.4 g of anhydrous sodium acetate was added to the above solution. The above solution was stirred for 30 min and then transferred to a closed polytetrafluoroethylene reactor for 12 h at 200 °C. Then, the reactor was cooled to room temperature. The black precipitate was collected using a magnetic block and repeatedly washed with deionized water and ethanol. Then, the obtained black powder was dried under vacuum at 60 °C for 6 h.

2.3 Synthesis of Fe_3O_4 @PGFR

The prepared Fe_3O_4 particles (0.08 g) and pyrogallol (0.1637 g) were uniformly dispersed in 200 mL of a deionized water solution containing 142 μL of ammonia and stirred well. Then, a formaldehyde solution (222 μL) was added to the solution, dispersed evenly by stirring for 30 minutes, heated to 80 °C, and maintained for 30 minutes. After the completion of the reaction, Fe_3O_4 @PGFR was thoroughly washed with deionized water and ethanol, separated using a magnet, and dried under vacuum for 6 h.

2.4 Synthesis of Fe_3O_4 @PGFR@Ag and Fe_3O_4 @PGFR@Ag-CTAB

The preparation procedure of the Fe_3O_4 @PGFR@Ag nano-material is as follows. The prepared Fe_3O_4 @PGFR (25 mg) was

dispersed in 50 mL of an aqueous silver nitrate (2 mM) solution and stirred at room temperature in a dark environment for 2 hours. Fe_3O_4 @PGFR@Ag was washed several times with deionized water and ethanol, magnetically separated, and dried under vacuum for 6 hours. The charge conversion of Fe_3O_4 @PGFR@Ag NPs was achieved by immersing Fe_3O_4 @PGFR@Ag in a CTAB solution for 24 hours (named as Fe_3O_4 @PGFR@Ag-CTAB). The synthesis route is shown in Fig. 1.

2.5 Characterization

The transmission electron microscopy (TEM) images were obtained using JEM-2100F. Scanning electron microscopy (SEM) images were obtained using a Zeiss Merlin compact field-emission instrument at an accelerating voltage of 20 kV. The Fourier-transform infrared (FTIR) spectra were recorded on a Bruker Equinox 55 spectrometer in the transmission mode in the scan range from 4000 to 500 cm^{-1} . The UV-vis absorption spectra were recorded on a UV-3600 spectrophotometer (Shimadzu, Japan). The zeta potentials were measured using a NanoBrook 90Plus Zeta nanograin-sized analyzer (Brookhaven, USA). The magnetic characteristics of the samples were studied using a vibrating sample magnetometer (VSM) (HH-20, China) at an applied field between -1500 and 1500 Oe at room temperature. The X-ray diffraction (XRD) patterns were measured using an XRD-6000 X-ray diffractometer (Shimadzu, Japan). X-ray photoelectron spectroscopy (XPS) results were recorded on an Axis Ultra DLD system using Al $\text{K}\alpha$ radiation.

2.6 Catalytic performance test

Initially, an aqueous solution of Fe_3O_4 @PGFR@Ag was prepared at a concentration of 0.25 mg mL^{-1} . Subsequently, the aqueous Fe_3O_4 @PGFR@Ag solution (200 μL) was added to a mixed solution containing 2 mL of RhB (10 mg mL^{-1}) and 1 mL of a freshly prepared sodium borohydride (0.5 M) solution. The concentration change of the solution was monitored using a UV-vis spectrometer. The catalytic activity of Fe_3O_4 @PGFR@Ag for RhB was evaluated using a quasi-level kinetic equation. The same procedure was followed for methyl orange

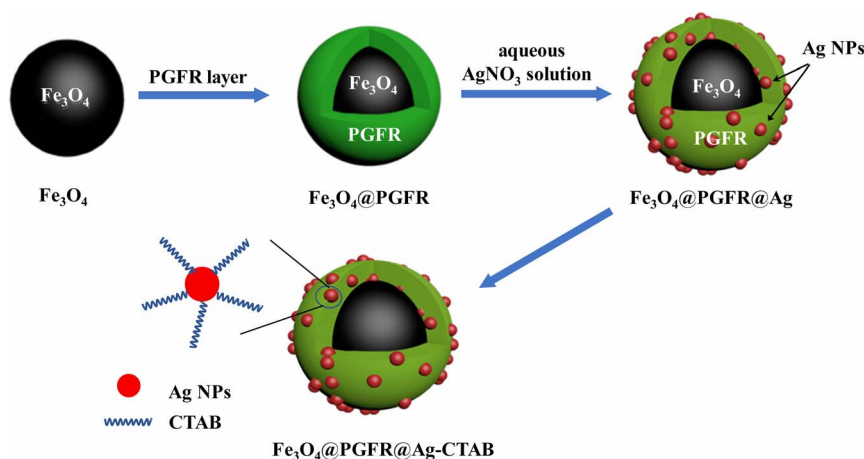


Fig. 1 Synthesis route for Fe_3O_4 @PGFR@Ag-CTAB core-shell nanomaterials.



and tetracycline. To assess the catalytic cyclability of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$, an aqueous solution of the contaminant (1 mg mL^{-1} , $20 \text{ }\mu\text{L}$) was added to the reaction system for the next catalytic cycle. The catalytic performance of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ NPs was evaluated using the same method.

3. Results and discussion

3.1 Characterization of $\text{Fe}_3\text{O}_4\text{@PGFR}$, $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$, and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$

The SEM and TEM images of Fe_3O_4 , $\text{Fe}_3\text{O}_4\text{@PGFR}$, and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ are presented in Fig. 2. As shown in Fig. 2a, Fe_3O_4 NPs exhibited a regular and uniform spherical structure with a relatively rough surface. After coating Fe_3O_4 NPs with PGFR (Fig. 2c), $\text{Fe}_3\text{O}_4\text{@PGFR}$ core-shell nanoparticles were formed, with PGFR uniformly coating the surface of Fe_3O_4 NPs. The surface of $\text{Fe}_3\text{O}_4\text{@PGFR}$ became smooth, and the thickness of the PGFR layer was approximately 30 nm (Fig. 2d). The TEM image of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ (Fig. 2f) revealed that Ag NPs were successfully captured and immobilized within the shell of PGFR. This suggests that the phenolic hydroxyl groups in the PGFR layer can form coordination complexes with silver ions and reduce them to silver nanoparticles, which then grow on the PGFR shell.

The TEM images of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ prepared with different silver nitrate contents and the Ag^0 particle size distributions are shown in Fig. 3. The results indicate that the particle size of Ag NPs increased with an increase in the AgNO_3 dosage. With an increase in the dosage of AgNO_3 , a higher amount of Ag^+ diffused into the shell layer of PGFR, where it was captured and anchored for reduction deposition. It is also owing to its adhesion properties that $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ aggregation occurs. The overall size distribution of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ is shown in Fig. 4.

The X-ray diffraction (XRD) patterns of Fe_3O_4 , $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$, and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ nanomaterials are shown in Fig. 5. The seven peaks at 18.3° , 30.1° , 35.8° , 43.1° , 54.4° , 57.0° , and 62.6° corresponded to the (1 1 1), (2 2 0), (3 1 1), (4 4 0), (4 2 2), (5 1 1), and (4 4 0) planes of Fe_3O_4 , respectively (JCPDS card no. 19-0629). The XRD pattern of the

$\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ nanohybrid material also confirmed the presence of Ag NPs with four new peaks at 38.1° , 44.3° , 64.4° , and 77.5° , corresponding to the (111), (200), (220), and (311) planes of Ag NPs, respectively (JCPDS card no. 04-0783). The XRD patterns of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ did not differ significantly. This indicates that surface modification by CTAB does not affect the crystalline shape and the presence of Ag NPs. Ag NPs can still maintain their good catalytic activity. The HRTEM images of Ag NPs are shown in Fig. 5b. According to Image J calculations, the lattice spacing of Ag NPs was 0.238 nm (Fig. 5c), corresponding to the (111) crystal plane of the face-centered cubic (fcc) structure. The diffraction spots (Fig. 5c) are the FFT of the areas marked by the red box in Fig. 5b.

FT-IR spectroscopy was employed to investigate the chemical structure of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ core-shell materials. The spectra of the samples are presented in Fig. 6. The peak observed at 580 cm^{-1} corresponded to the stretching vibration of the Fe-O bond in pure Fe_3O_4 NPs (Fig. 6a). The two peaks observed at 1305 cm^{-1} and 1112 cm^{-1} corresponded to the stretching vibrations of the C-O bond and the C-O-C vibrational mode, respectively, indicating the presence of the PGFR coating on Fe_3O_4 NPs. As shown in Fig. 6c and d, $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ exhibited four additional distinct peaks at 910 cm^{-1} , 957 cm^{-1} , 2845 cm^{-1} , and 2913 cm^{-1} compared to $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$. The peaks at 910 cm^{-1} and 957 cm^{-1} were attributed to the in-plane C-H bending vibrations, while the peak at 2845 cm^{-1} corresponded to the stretching vibration of $-\text{CH}_2-$. The peak at 2913 cm^{-1} was assigned to the C-H stretching vibration of the saturated carbon of the CTAB end group ($-\text{CH}_3$). These results confirm the successful preparation of the $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$ nanohybrid materials.

To further demonstrate the presence of silver as a monomer in the hybrid material, the X-ray photoelectron spectroscopy (XPS) spectra of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ nanomaterials were recorded and are presented in Fig. 7. The full-scan XPS spectra of the samples showed the presence of the O 1s orbital, C 1s orbital, and Ag 3d orbital. The high-resolution XPS spectrum of Ag 3d in Fig. 7b revealed that the 3/2 and 5/2 peaks of the Ag 3d orbital were located at 374.2 eV and 368.3 eV, respectively. Previous

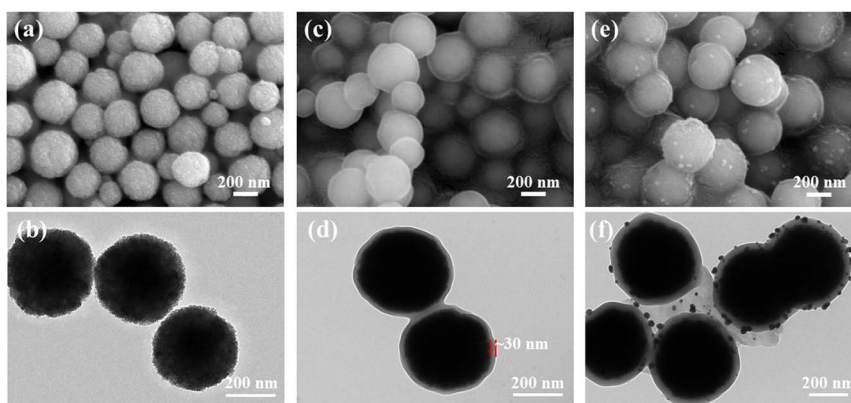


Fig. 2 SEM and TEM images. (a) SEM image of Fe_3O_4 , (b) TEM image of Fe_3O_4 , (c) SEM image of $\text{Fe}_3\text{O}_4\text{@PGFR}$, (d) TEM image of $\text{Fe}_3\text{O}_4\text{@PGFR}$, (e) SEM image of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$, and (f) TEM image of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$.

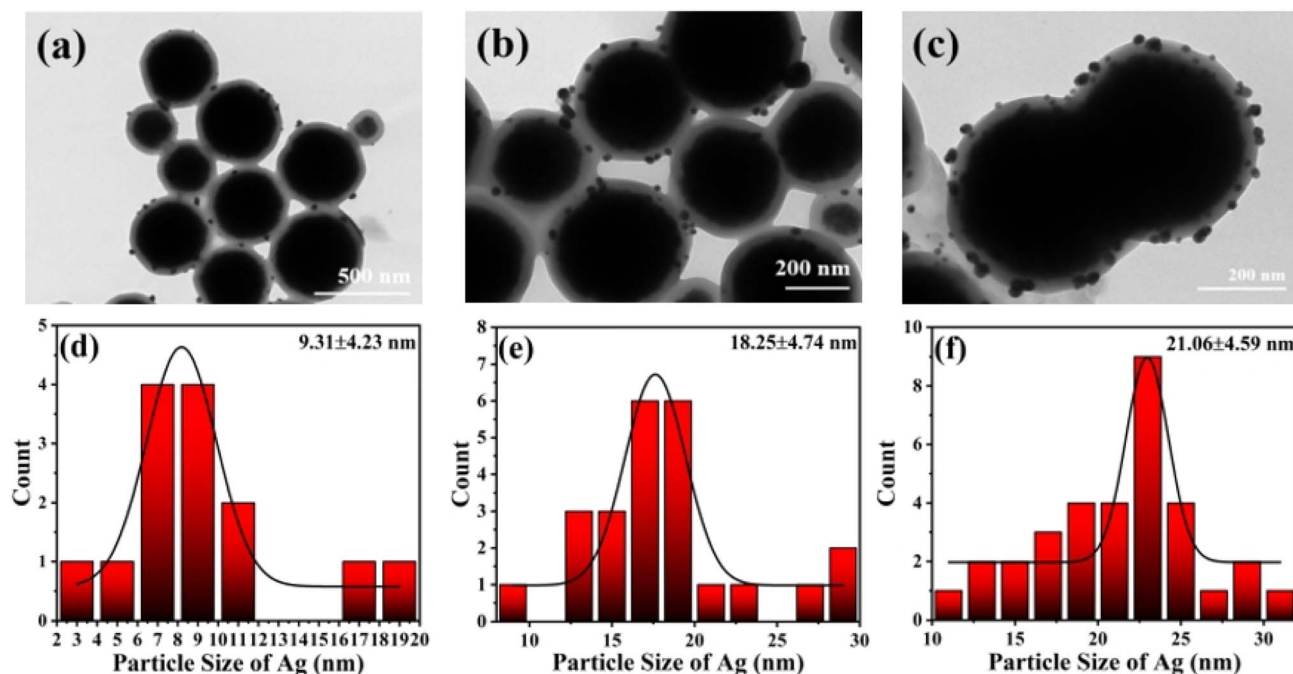


Fig. 3 TEM images of (a) $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ -0.5 mM, (b) $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ -1 mM, and (c) $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ -2 mM. (d) Particle size distribution of Ag NPs-0.5 mM, (e) particle size distribution of Ag NPs-1 mM, and (f) particle size distribution of Ag NPs-2 mM.

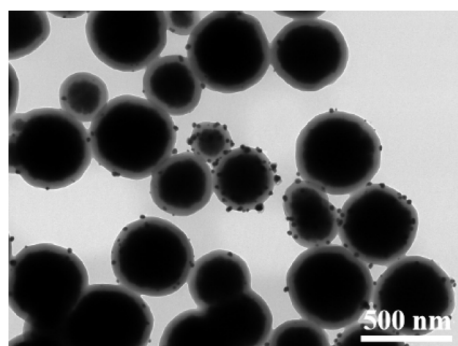


Fig. 4 Overall size distribution of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ -CTAB.

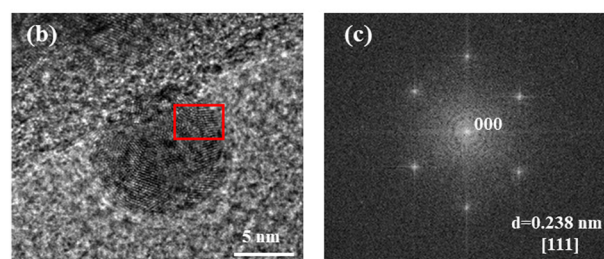
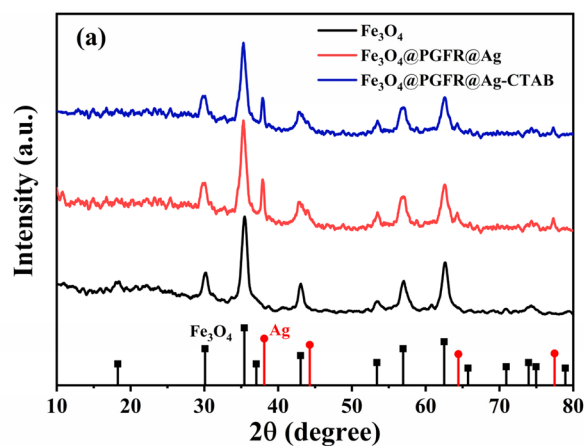


Fig. 5 (a) XRD patterns of Fe_3O_4 , $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$, and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag-CTAB}$. (b) HRTEM image of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$. (c) FFT of $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$.

reports have shown that the single silver peak corresponds to a binding energy of around 370 eV, which is typical for metallic silver. This confirms that the metallic silver presented in the $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ nanohybrid material is the active material required for subsequent catalysis. XPS further confirmed that silver in the hybrid material existed as a monomer. Fig. 7c shows three peaks based on the C 1s fitted deconvolution, with C 1s binding energies at 284.2 eV, 285.5 eV, and 288.0 eV, corresponding to the C–C bond, C–O bond, and C=O double bond of PGFR, respectively. The TEM image (Fig. 2f) demonstrated the successful encapsulation of Fe_3O_4 by the PGFR layer. Ag NPs were reduced by capturing Ag^+ using the phenolic hydroxyl group, which facilitated the growth of Ag NPs on the PGFR shell layer.

The thermogravimetric (TG) curves of Fe_3O_4 , $\text{Fe}_3\text{O}_4\text{@PGFR}$, and $\text{Fe}_3\text{O}_4\text{@PGFR@Ag}$ nanomaterials are presented in Fig. 8a.

Catalytic reactions often occur in complex environments, such as high temperatures and heat, and the thermal stability of materials can have a significant impact on their catalytic



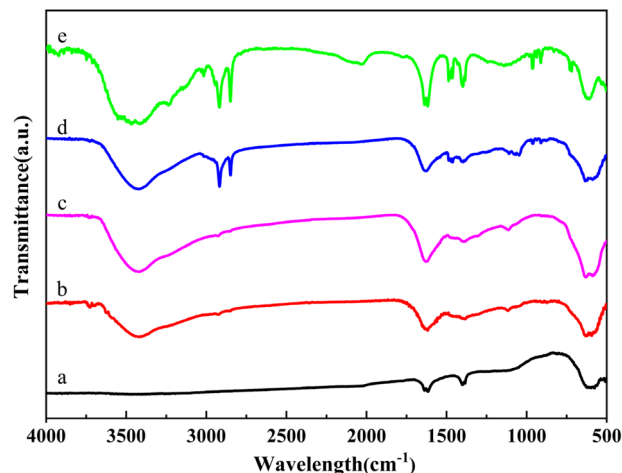


Fig. 6 FT-IR spectra of (a) Fe_3O_4 , (b) Fe_3O_4 @PGFR, (c) Fe_3O_4 @PGFR@Ag, (d) Fe_3O_4 @PGFR@Ag-CTAB, and (e) CTAB.

performance. As shown in Fig. 8a, when the temperature was below 160 °C, the weight loss of Fe_3O_4 nanoparticles was due to the evaporation of residual water and organic solvents in the material during the heating process. In the temperature range

from 200 °C to 270 °C, the weight loss of the sample was attributed to thermal decomposition and carbonization caused by the thermal degradation and carbonization of trisodium citric acid, which served as a stabilizer for iron tetroxide. For Fe_3O_4 @PGFR, the approximately 43.5 wt% mass loss was mainly due to the carbonization of the PGFR shell when the temperature increased to around 700 °C. The rapid weight loss of Fe_3O_4 @PGFR at approximately 700 °C was attributed to the collapse of its core-shell structure.

The mass loss of Fe_3O_4 @PGFR@Ag was approximately 39.7 wt%, which is lower than that of Fe_3O_4 @PGFR nanoparticles. As shown in Fig. 8a, Fe_3O_4 @PGFR and Fe_3O_4 @PGFR@Ag exhibited similar weight loss stages from 200 °C to 800 °C, but they differed significantly from pure Fe_3O_4 . This indicates that the PGFR shell layer is successfully encapsulated around Fe_3O_4 and Ag NPs are grown *in situ* on the PGFR shell layer. The presence of the PGFR layer had a significant effect on the thermal stability of the catalytic materials. The magnetic properties of the samples were characterized by VSM, as shown in Fig. 8b. The saturation magnetization of pure Fe_3O_4 was measured to be 34.5 emu g^{-1} . After coating with PGFR, Fe_3O_4 @PGFR exhibited a reduced magnetization of 18.3 emu g^{-1} . Fe_3O_4 @PGFR@Ag displayed a slight decrease in magnetization (16.9 emu g^{-1}). This reduction did not significantly impact the

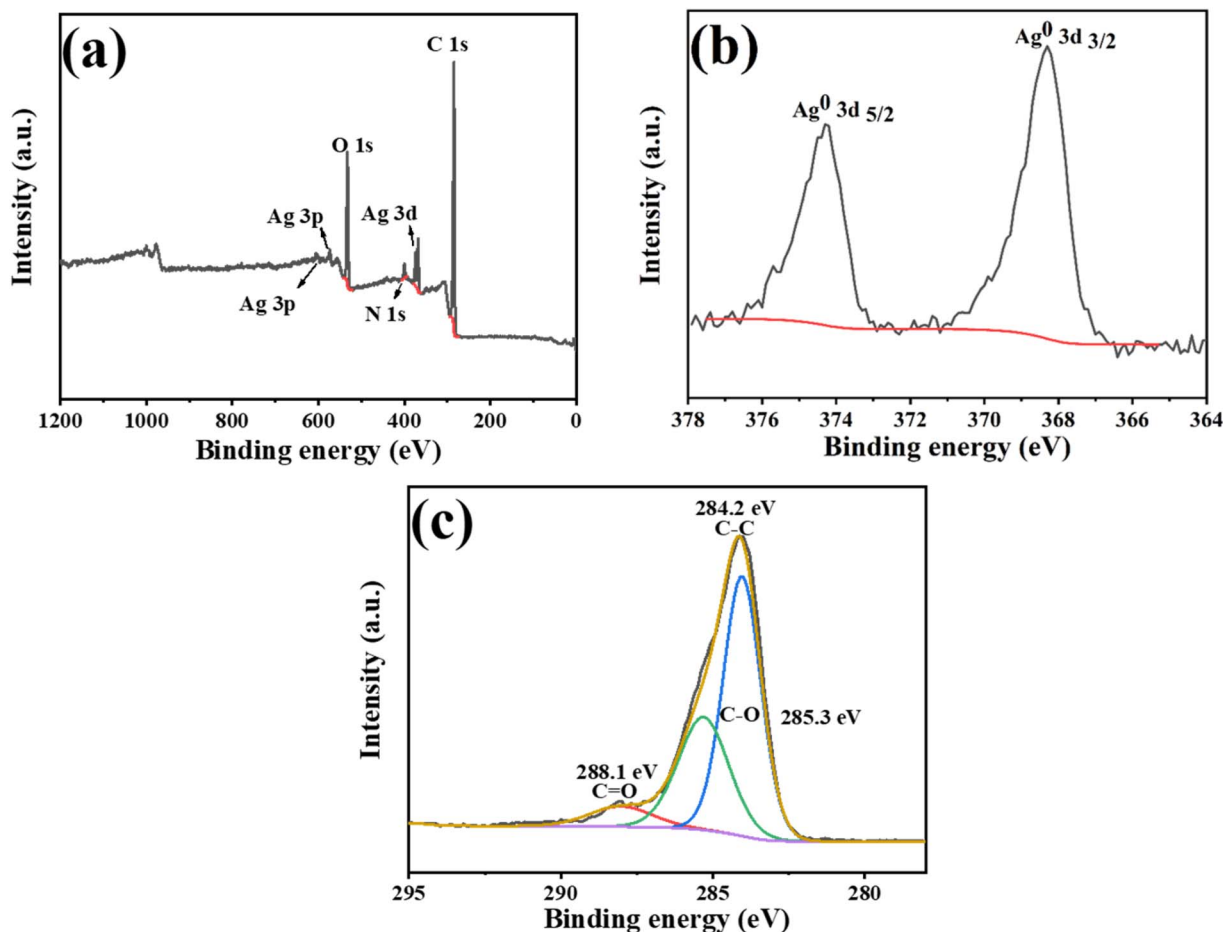


Fig. 7 XPS spectra of Fe_3O_4 @PGFR@Ag: (a) full-scan, (b) Ag 3d, and (c) C 1s spectra.

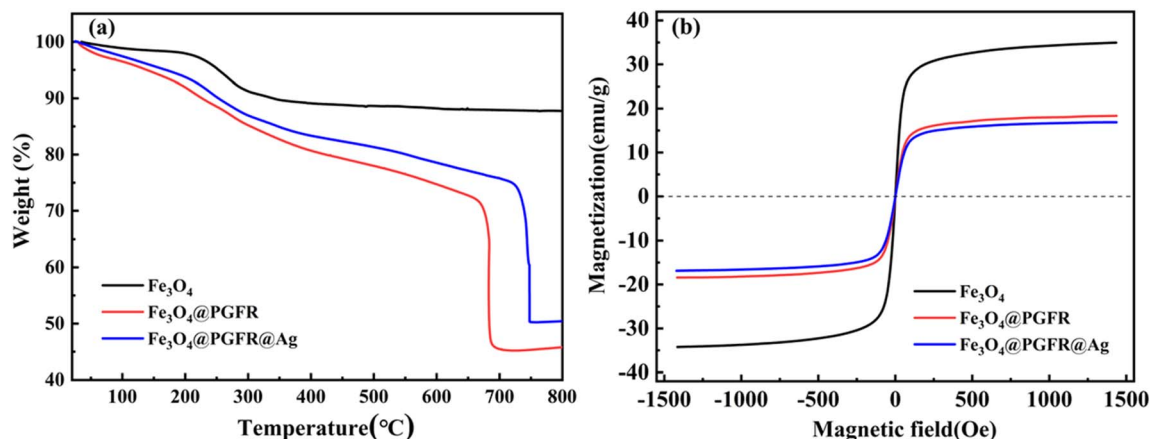


Fig. 8 (a) TG curves of Fe₃O₄, Fe₃O₄@PGFR, and Fe₃O₄@PGFR@Ag. (b) VSM curves of Fe₃O₄, Fe₃O₄@PGFR and Fe₃O₄@PGFR@Ag.

magnetic recovery performance of Fe₃O₄@PGFR@Ag, as evidenced by its efficient separation from the solution using an external magnetic field.

Fig. 9 shows the zeta potentials of Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB. The zeta potential of Fe₃O₄@PGFR@Ag was approximately −36.3 mV (Fig. 9). Due to the surface electrostatic attraction, a negative surface charge state would exhibit higher catalytic properties for cationic dyes such as RhB. Therefore, changing the surface charge state of the nanomaterial is crucial for preparing nanomaterials with high catalytic performance for anionic dyes such as MO. CTAB, as a cationic surfactant, can combine with metal particles to form noble metal particle-CTAB. This allows the surface charge state of noble metal particles to transition from negative to positive. Fe₃O₄@PGFR@Ag-CTAB nanoparticles with a positive surface charge were obtained by modifying Fe₃O₄@PGFR@Ag with CTAB. The zeta potential of Fe₃O₄@PGFR@Ag-CTAB was approximately 15.1 mV (Fig. 9). The XRD pattern of Fe₃O₄@PGFR@Ag-CTAB did not differ significantly from that of Fe₃O₄@PGFR@Ag (Fig. 5), indicating that modification with CTAB only changed the surface charge state of the materials without

altering the structure of Fe₃O₄@PGFR@Ag-CTAB or the presence state of Ag NPs.

3.2 Catalytic properties of Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB

Silver nanoparticles have been reported to exhibit excellent catalytic activity and good selectivity towards organic dyes. Therefore, we investigated the catalytic performance of Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB towards MO, RhB, and TC in the presence of NaBH₄. Fig. 10a shows a schematic diagram of the catalytic process for the three substrate models. In brief, the catalysis of the three substrates, which are enriched on the surface of Ag NPs, is achieved *via* the transfer of free electrons of Ag NPs. The UV-vis spectra of MO catalyzed by Fe₃O₄@PGFR@Ag are presented in Fig. 10b. It can be observed that after the addition of 200 μL of the Fe₃O₄@PGFR@Ag catalyst into the catalytic system, the intensity of the characteristic peak of MO at 465 nm began to decrease, and the intensity of the characteristic peak decreased with increasing catalytic time. When the catalyst was added for approximately 3 minutes, the peak of MO at 465 nm disappeared completely, indicating that the catalytic reaction was completed and MO had been reduced. The catalytic rate of Fe₃O₄@PGFR@Ag for MO was 1.564 min^{−1}. When 200 μL of the Fe₃O₄@PGFR@Ag-CTAB catalyst was added to the MO solution, the characteristic peak of MO at 465 nm rapidly decreased and disappeared within approximately 1 minute. The catalytic rate of Fe₃O₄@PGFR@Ag-CTAB for MO was 3.510 min^{−1}. These results demonstrate that positively charged Fe₃O₄@PGFR@Ag-CTAB significantly enhances the catalytic rate for the anionic dye MO. The MO molecule is enriched on the surface of Ag NPs due to electrostatic effects. This facilitates the rapid acceptance of free electrons generated from the hydrolysis of NaBH₄, which is attacked by free electrons, and the N=N bonds break to form N-H bonds.

To further analyze the effect of the surface charge state of the catalytic material on its catalytic performance, we conducted comparative catalytic experiments using the cationic dye RhB. As shown in Fig. 10e, the intensity of the characteristic peak of

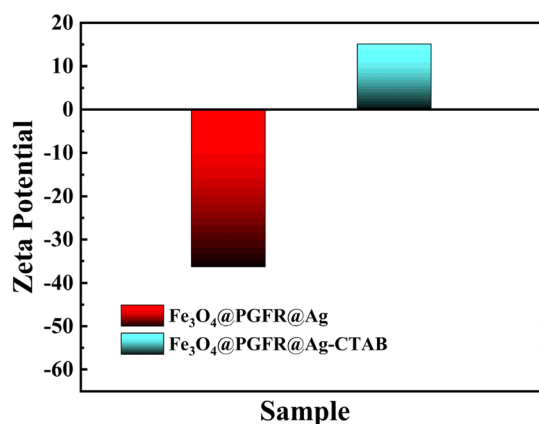


Fig. 9 Zeta potentials of Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB.



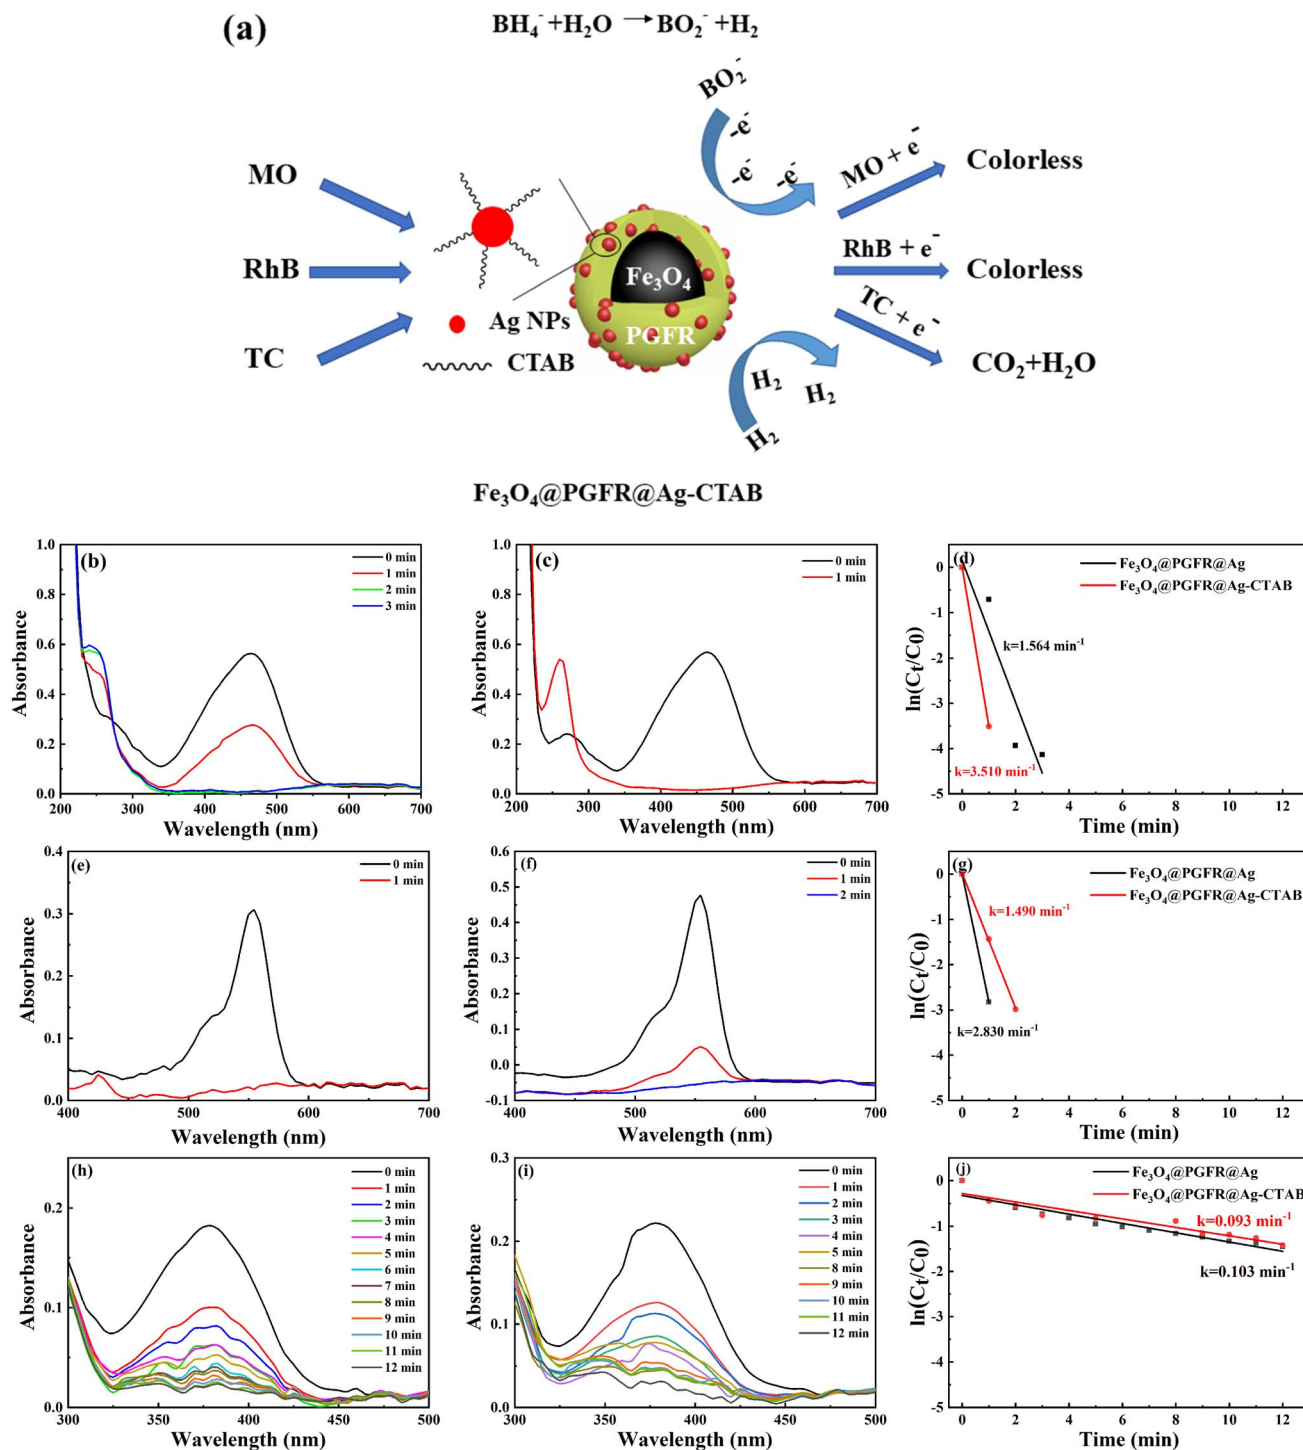


Fig. 10 (a) Schematic of the catalytic process. UV-vis spectra for MO: (b) $\text{Fe}_3\text{O}_4@PGFR@Ag$ and (c) $\text{Fe}_3\text{O}_4@PGFR@Ag-CTAB$. (d) Comparison of first-order rates of reductive degradation. UV-vis spectra for RhB: (e) $\text{Fe}_3\text{O}_4@PGFR@Ag$ and (f) $\text{Fe}_3\text{O}_4@PGFR@Ag-CTAB$. (g) Comparison of first-order rates of reductive degradation. UV-vis spectra for TC: (h) $\text{Fe}_3\text{O}_4@PGFR@Ag$ and (i) $\text{Fe}_3\text{O}_4@PGFR@Ag-CTAB$. (j) Comparison of first-order rates of reductive degradation.

RhB at 550 nm decreased rapidly after the catalyst was added. Due to the electrostatic effect, the cationic dye RhB was more easily enriched on the surface of $\text{Fe}_3\text{O}_4@PGFR@Ag$ with a negative surface charge. The cationic dye RhB was catalyzed, and new RhB molecules were re-attracted to the surface of Ag

NPs, reaching a kinetic equilibrium. The catalytic rate k was 2.830 min^{-1} , according to the fitting of the first-order kinetic equation. For $\text{Fe}_3\text{O}_4@PGFR@Ag-CTAB$ (Fig. 10f), the positive surface charge was retarded due to the aggregation of RhB molecules on Ag NPs, which delayed the time required for RhB

Table 1 Catalytic rates of the samples for MO, RhB, and TC

Sample	<i>k</i> for RhB (min ⁻¹)	<i>k</i> for MO (min ⁻¹)	<i>k</i> for TC (min ⁻¹)
Fe ₃ O ₄ @PGFR@Ag	2.830	1.564	0.103
Fe ₃ O ₄ @PGFR@Ag-CTAB	1.490	3.510	0.093

Table 2 Comparison of the TC catalytic degradation performance of different catalytic materials

Sample	TC	Catalyst dosage	<i>k</i> (min ⁻¹)	Ref.
Fe ₃ O ₄ /BiVO ₄ /CdS	10 mg L ⁻¹	100 mg	0.023	37
Fe ₃ O ₄ /CuO/C	50 mg L ⁻¹	300 mg	0.923	38
Bi ₂ O ₃ QDs/g-C ₃ N ₄	10 mg L ⁻¹	50 mg	0.014	39
Ag-g-C ₃ N ₄	20 mg L ⁻¹	50 mg	0.041	40
AgI/Ag/Cu-BTC	5 mg L ⁻¹	80 mg	0.022	5
Fe ₃ O ₄ @PGFR@Ag-CTAB	2 mL, 10 mg L ⁻¹	0.25 mg mL ⁻¹ , 200 µL (0.05 mg)	0.103	This work

molecules to reach the Ag NP surface. The catalytic rate constant (*k*) was calculated to be 1.490 min⁻¹; notably, this value was lower than that of Fe₃O₄@PGFR@Ag (*k* = 2.830 min⁻¹). The catalytic rate constants for the three pollutants are presented in Table 1. The surface charge state of the samples had a significant impact on the catalytic performance of the pollutants. In the case of catalysts and contaminants with opposite charges, the contaminants tended to accumulate around the catalyst owing to electrostatic attraction and subsequently undergo further decolorization and degradation by Ag. However, when the charge state of the catalyst and the contaminant was the same, the contaminants were less likely to accumulate around the catalyst owing to electrostatic repulsion, and the catalytic reaction rate constant was significantly reduced.

To evaluate the catalytic performance of Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB, neutral tetracycline (TC) was selected as a test substrate. As shown in Fig. 10h, the intensity of the characteristic peak at 380 nm decreased with the progress of the reaction and disappeared after approximately 12 minutes.

Compared with Fe₃O₄@PGFR@Ag, the catalytic capacity of Fe₃O₄@PGFR@Ag-CTAB for TC did not differ significantly. According to the fitting calculation of the first-order kinetic equation (Fig. 10j), the catalytic rate constants of Fe₃O₄@PGFR@Ag nanoparticles and Fe₃O₄@PGFR@Ag-CTAB nanoparticles for TC were 0.103 min⁻¹ and 0.093 min⁻¹, respectively (Table 1). These results indicate that switching the material surface charge has little effect on the catalytic performance of neutral TC.

The catalytic properties of various catalytic materials for MO, RhB, and TC are summarized in Tables 2–4, respectively. Compared to the catalysts reported in previous studies, Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB exhibited superior catalytic performance.

3.3 Stability and recyclability

To assess the stability and recyclability of the catalytic materials, Fe₃O₄@PGFR@Ag-CTAB was employed to catalyze MO. Six

Table 3 Comparison of the MO catalytic degradation performance of different catalytic materials

Sample	MO	Catalyst dosage	<i>k</i> (min ⁻¹)	Ref.
GO/TiO ₂ /Fe ₃ O ₄	50 mL, 10 mg L ⁻¹	60 mg	0.022	41
Au-TA	50 mL, 8 mg L ⁻¹	50 µL	0.005	42
Ag-TA	50 mL, 8 mg L ⁻¹	50 µL	0.59	42
Fe ₃ O ₄ @C@Au-CTAB	0.25 mg L ⁻¹	1 mg	1.870	25
Fe ₃ O ₄ @PGFR@Ag-CTAB	2 mL, 10 mg L ⁻¹	0.25 mg mL ⁻¹ , 200 µL (0.05 mg)	3.510	This work

Table 4 Comparison of the RhB catalytic degradation performance of different catalytic materials

Sample	RhB	Catalyst dosage	<i>k</i> (min ⁻¹)	Ref.
F-CeO ₂ /CdS	50 mL, 10 mg L ⁻¹	50 mg	0.036	43
BN/C ₃ N ₄	50 mL, 5 mg L ⁻¹	100 mg	0.072	44
Pd-TiO ₂ /Bi ₂ O ₃	10 mg L ⁻¹	50 mg	0.110	45
Fe ₃ O ₄ @C@Au-CTAB	0.25 mg L ⁻¹	1 mg	0.500	25
Fe ₃ O ₄ @PGFR@Ag-CTAB	2 mL, 10 mg L ⁻¹	0.25 mg mL ⁻¹ , 200 µL (0.05 mg)	0.103	This work



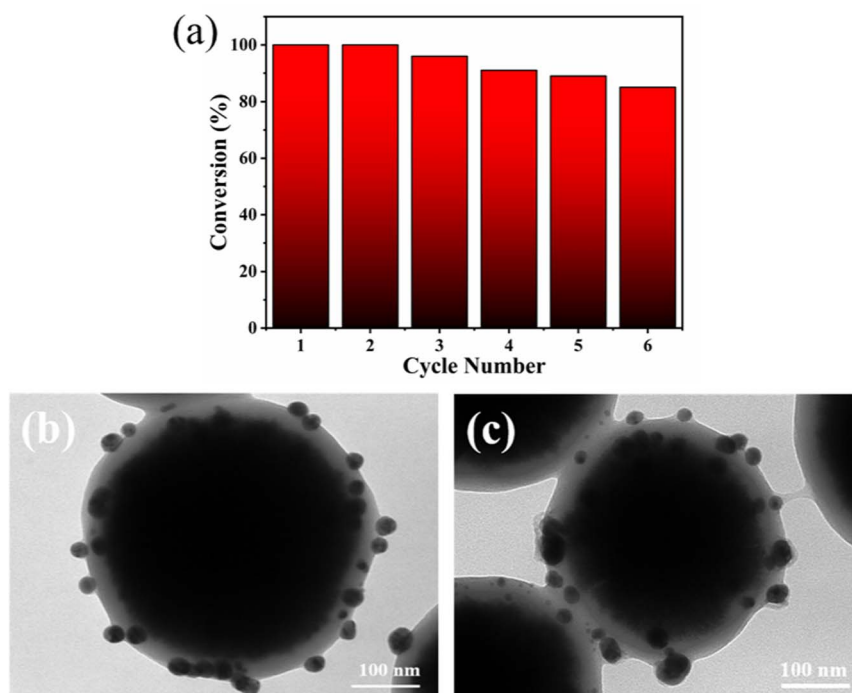


Fig. 11 Cycle performance. (a) Catalytic reuse efficiency. TEM images of Fe₃O₄@PGFR@Ag-CTAB (b) before the cycle and (c) after six cycles.

cycling experiments were carried out. As shown in Fig. 11a, Fe₃O₄@PGFR@Ag-CTAB nanoparticles exhibited an efficient catalytic capacity for MO, which was sustained at approximately 85%. This indicated that Fe₃O₄@PGFR@Ag-CTAB nanoparticles possessed an effective cycling capacity and stability for MO. Furthermore, as shown in Fig. 11c, after multiple cycles, the Ag NPs in Fe₃O₄@PGFR@Ag-CTAB nanoparticles did not exhibit significant shedding and the structure remained intact. The sustainability of catalytic materials was confirmed by the presence of silver nanoparticles and the integrity of the core-shell structure. The cyclic tests demonstrated that PGFR was an ideal carrier for Ag NPs, which could achieve the efficient and continuous chelation and anchoring of Ag NPs. The CTAB-modified Fe₃O₄@PGFR@Ag nanoparticles maintained efficient catalytic activity for MO in cycling tests, and the structure of the catalytic materials remained intact during the reaction process.

4. Conclusions

In this work, Fe₃O₄@PGFR@Ag core-shell nanomaterials were successfully prepared with controlled charge switching using a facile CTAB modification method. Fe₃O₄@PGFR@Ag-CTAB exhibited efficient catalytic properties towards the anionic dye MO, which was attributed to favorable electrostatic interactions. The catalytic rate constant of Fe₃O₄@PGFR@Ag-CTAB for MO was found to be 3.510 min⁻¹, 124% higher than that of Fe₃O₄@PGFR@Ag. Similarly, the *k* value for the cationic dye RhB of Fe₃O₄@PGFR@Ag was 2.83 min⁻¹, which was 90% higher than that of positively charged Fe₃O₄@PGFR@Ag-CTAB. Moreover, Fe₃O₄@PGFR@Ag and Fe₃O₄@PGFR@Ag-CTAB showed similar

catalytic degradation efficiencies towards the neutral antibiotic TC. These results demonstrated that the catalytic activity was not only dependent on the property of the catalyst but also on the charge state of the contaminant.

Data availability

The authors affirm that the data supporting the findings of this study are included in the article. Additional data can be made available from the corresponding author upon reasonable request.

Author contributions

Liping Jiang: data curation, formal analysis, methodology, and writing – original draft. Yang Xi: data curation, formal analysis, and writing – review & editing. Ziyi Xu: investigation and methodology. Zewen Song: investigation and methodology. Yuwei Cui: formal analysis and investigation. Haijun Zhou: data curation, funding acquisition, project administration, supervision, and writing – review & editing.

Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

This work was supported by Jiangsu University of Science and Technology.

References

- 1 V. K. M. Au, Recent advances in the use of metal-organic frameworks for dye adsorption, *Front. Chem.*, 2020, **8**, 708, DOI: [10.3389/fchem.2020.00708](#).
- 2 P. Zhang, J. Liu, Y. Qu, W. He and Y. Feng, Nanomaterials for facilitating microbial extracellular electron transfer: Recent progress and challenges, *Bioelectrochemistry*, 2018, **123**, 190–200, DOI: [10.1016/j.bioelechem.2018.05.005](#).
- 3 M. Pirzada and Z. Altintas, Nanomaterials for healthcare biosensing applications, *Sensors*, 2019, **19**(23), 5311, DOI: [10.3390/s19235311](#).
- 4 Y. T. Assatse, G. W. Ejub, F. Tchoffo and J. M. B. Ndjaka, DFT studies of nanomaterials designed by the functionalization of modified carboxylated carbon nanotubes with biguanide derivatives for nanomedical, nonlinear and electronic applications, *Chin. J. Phys.*, 2019, **58**(2), 253–262, DOI: [10.1016/j.cjph.2019.01.014](#).
- 5 H. Yu, H. Yin, L. Wang, S. Zhao, J. Gong, Z. Ji, Y. Zheng and Q. Nie, Construction of MOFs-based AgI/Ag/Cu₃(BTC)₂ ternary composites as Z-scheme photocatalysts for effective degradation of tetracycline, *Bull. Mater. Sci.*, 2021, **44**(2), 127, DOI: [10.1007/s12034-021-02414-5](#).
- 6 M. S. Samuel, S. Jose, E. Selvarajan, T. Mathimani and A. Pugazhendhi, Biosynthesized silver nanoparticles using *Bacillus amyloliquefaciens*; Application for cytotoxicity effect on A549 cell line and photocatalytic degradation of p-nitrophenol, *J. Photochem. Photobiol., B*, 2020, **202**, 111642, DOI: [10.1016/j.jphotobiol.2019.111642](#).
- 7 X. Kang, D. Teng, S. Wu, Z. Tian, J. Liu, P. Li, Y. Ma and C. Liang, Ultrafine copper nanoparticles anchored on reduced graphene oxide present excellent catalytic performance toward 4-nitrophenol reduction, *J. Colloid Interface Sci.*, 2020, **566**, 265–270, DOI: [10.1016/j.jcis.2020.01.097](#).
- 8 K. R. Mohammadzadeh, R. Tayebbe and S. Hedayat, Phthalhydrazide nanoparticles as new highly reusable organic photocatalyst in the photodegradation of organic and inorganic contaminants, *Appl. Organomet. Chem.*, 2017, **32**(2), e4033, DOI: [10.1002/aoc.4033](#).
- 9 Y. Xu, L. Guo, H. Zhang, H. Zhai and H. Ren, Research status, industrial application demand and prospects of phenolic resin, *RSC Adv.*, 2019, **9**, 28924–28935, DOI: [10.1039/c9ra06487g](#).
- 10 I. Do and L. Drzal, Room temperature ionic liquids for size control of noble metal nanoparticles on carbon supports, *Carbon*, 2014, **75**(15), 43–55, DOI: [10.1016/j.carbon.2014.02.067](#).
- 11 H. He, J. Li, C. Yu and Z. Luo, Surface decoration of microdisk-like g-C₃N₄/diatomite with Ag/AgCl nanoparticles for application in Cr(VI) reduction, *Sustainable Mater. Technol.*, 2019, **22**, e00127, DOI: [10.1016/j.susmat.2019.e00127](#).
- 12 S. Xie, J. Jiang, G. Zhou, Y. Chen, A. Zhang, X. Xia, M. Shi, B. Deng, C. Yu and H. He, Optimizing electronic structure through lattice engineering for enhanced photocatalytic reduction of Cr(VI), *Inorg. Chem. Commun.*, 2025, **173**, 113845, DOI: [10.1016/j.inoche.2024.113845](#).
- 13 H. He, J. Jiang, Z. Luo, D. Li, M. Shi, H. Sun, J. Chen, C. Chen, B. Deng and C. Yu, Novel starfish-like inorganic/organic heterojunction for Cr(VI) photocatalytic reduction in neutral solution, *Colloids Surf., A*, 2023, **667**, 131357, DOI: [10.1016/j.colsurfa.2023.131357](#).
- 14 X. Zhang, S. Si, X. Zhang, W. Wu, X. Xiao and C. Jiang, Improved thermal stability of graphene-veiled noble metal nanoarrays as recyclable SERS substrates, *ACS Appl. Mater. Interfaces*, 2017, **9**(46), 40726–40733, DOI: [10.1021/acsami.7b13708](#).
- 15 J. S. Kim, Production, separation, and applications of phenolic-rich bio-oil-A review, *Bioresour. Technol.*, 2015, **178**(11), 90–98, DOI: [10.1016/j.biortech.2014.08.121](#).
- 16 R. Liu and R. D. Priestley, Rational design and fabrication of core-shell nanoparticles through a one-step/pot strategy, *J. Mater. Chem. A*, 2016, **4**(18), 6680–6692, DOI: [10.1039/C5TA09607C](#).
- 17 S. K. Warkhade, R. S. Das, G. S. Gaikwad, U. R. Pratap, S. P. Zodape and A. V. Wankhade, A facile microwave assisted fabrication of nano AgZrO₃: An efficient visible light harvesting photocatalyst, *Environ. Prog. Sustainable Energy*, 2019, **38**(3), e13071, DOI: [10.1002/ep.13071](#).
- 18 N. Wang, F. Xiao, J. Zhang, H. Zhou, Y. Qin and D. Pan, Spherical montmorillonite-supported nano-silver as a self-sedimentary catalyst for methylene blue removal, *Appl. Clay Sci.*, 2019, **174**, 146–151, DOI: [10.1016/j.clay.2019.03.021](#).
- 19 P. Liu and M. Zhao, Silver nanoparticle supported on halloysite nanotubes catalyzed reduction of 4-nitrophenol (4-NP), *Appl. Surf. Sci.*, 2009, **255**(7), 3989–3993, DOI: [10.1016/j.apsusc.2008.10.094](#).
- 20 S. Tang, H. Liu, M. Wang, S. Wang, C. Wang, C. Gu, Z. Zhao, T. Jiang and J. Zhou, Further enhancement of SERS signals from Au@Ag@PSPAA core-shell nanoparticles surrounded by Ag nanoplates, *Mater. Chem. Phys.*, 2019, **225**, 60–63, DOI: [10.1016/j.matchemphys.2018.12.040](#).
- 21 K. Tan, D. Sun, J. Huang, T. O. Wubah and Q. Li, State of arts on the bio-synthesis of noble metal nanoparticles and their biological application, *Chin. J. Chem. Eng.*, 2021, **30**, 272–290, DOI: [10.1016/j.cjche.2020.11.010](#).
- 22 Y. H. Kim, H. K. Park and Y. Ju, Fabrication of the novel Fe_{2+α}O_{3+α}-CoFe₂O₄ composite fibers and their magnetic properties, *J. Korean Ceram. Soc.*, 2020, **57**(4), 423–431, DOI: [10.1007/s43207-020-00040-1](#).
- 23 C. Parmar and G. S. Parmar, Structural and magnetic properties of six-line ferrihydrite nanoparticles, *J. Supercond. Novel Magn.*, 2020, **33**(2), 441–444, DOI: [10.1007/s10948-019-05200-x](#).
- 24 M. J. Molaei, Magnetic graphene, synthesis, and applications: A review, *Mater. Sci. Eng., B*, 2021, **272**, 115325, DOI: [10.1016/j.mseb.2021.115325](#).
- 25 C. Gong, Q. Li, H. Zhou and R. Liu, Tiny Au satellites decorated Fe₃O₄@3-aminophenol-formaldehyde core-shell nanoparticles: Easy synthesis and comparison in catalytic



- reduction for cationic and anionic dyes, *Colloids Surf., A*, 2018, **540**(6), 67–72, DOI: [10.1016/j.colsurfa.2017.12.045](#).
- 26 Y. Gao, J. Zhang, Z. Zhang, Z. Li, Q. Xiong, L. Deng, Q. Zhou, L. Meng, Y. Du, T. Zuo, Y. Yu, Z. Lan and P. Gao, Plasmon-enhanced perovskite solar cells with efficiency beyond 21%: The asynchronous synergistic effect of water and gold nanorods, *ChemPlusChem*, 2021, **86**(2), 291–297, DOI: [10.1002/cplu.202000792](#).
 - 27 L. Pu, J. Zhang, N. K. L. Jiresse, Y. Gao, H. Zhou, N. Naik, P. Gao and Z. Guo, N-doped MXene derived from chitosan for the highly effective electrochemical properties as supercapacitor, *Adv. Compos. Hybrid Mater.*, 2022, **5**, 356–369, DOI: [10.1007/s42114-021-00371-5](#).
 - 28 Y. Liu, H. Zhou, J. Wang, D. Yu, Z. Li and R. Liu, Facile synthesis of silver nanocatalyst decorated Fe₃O₄@PDA core-shell nanoparticles with enhanced catalytic properties and selectivity, *RSC Adv.*, 2022, **12**, 3847–3855, DOI: [10.1039/D1RA09187E](#).
 - 29 Y. Liu, H. Zhou, J. J. Wang, S. Li, Z. Li and J. Zhang, Core-shell Fe₃O₄@catechol-formaldehyde trapped satellite-like silver nanoparticles toward catalytic reduction in cationic and anionic dyes, *Vacuum*, 2022, **202**, 111204, DOI: [10.1016/j.vacuum.2022.111204](#).
 - 30 C. Gong, Z. Zhou, J. Li, H. Zhou and R. Liu, Facile synthesis of ultra stable Fe₃O₄@Carbon core-shell nanoparticles entrapped satellite Au catalysts with enhanced 4-nitrophenol reduction property, *J. Taiwan Inst. Chem. Eng.*, 2018, **84**, 229–235, DOI: [10.1016/j.jtice.2018.01.026](#).
 - 31 J. Zhang, P. Li, Z. Zhang, X. Wang, J. Tang, H. Liu, Q. Shao, T. Ding, A. Umar and Z. Guo, Solvent-free graphene liquids: Promising candidates for lubricants without the base oil, *J. Colloid Interface Sci.*, 2019, **542**, 159–167, DOI: [10.1016/j.jcis.2019.01.135](#).
 - 32 J. Zhang, J. Yi, Y. Jiao, S. Li, X. Shi and K. Sun, Preparation and application of water-soluble TiO₂-ionic liquids hybrid nanomaterials, *J. Inorg. Mater.*, 2018, **33**(5), 577–581, DOI: [10.15541/jim20170251](#).
 - 33 S. Guo, Q. Zhang, H. Li, H. Guo and W. He, Ag/C nanoparticles catalysed aerobic oxidation of diaryl and aryl(hetero) methylenes into ketones, *Nano Res.*, 2017, **10**(9), 3261–3267, DOI: [10.1007/s12274-017-1676-2](#).
 - 34 S. Li, L. Zhang, L. Zhang, J. Zhang, H. Zhou, X. Chen and T. Tang, The in-situ construction of three-dimensional core-shell-structured TiO₂@PPy/rGO nanocomposites for improved supercapacitor electrode performance, *New J. Chem.*, 2021, **45**(2), 1092–1099, DOI: [10.1039/D0NJ05328G](#).
 - 35 S. Li, L. Zhang, Y. Guo, Q. Zhang, M. Aleksandrak, E. Mijowska and X. Chen, Fabrication and characterization of a TiBs@MCN cable-like photocatalyst with high photocatalytic performance under visible light irradiation, *New J. Chem.*, 2022, **46**(13), 6319–6329, DOI: [10.1039/D2NJ00414C](#).
 - 36 S. Xuan, Y. Wang, J. Yu and K. C. F. Leung, Tuning the grain size and particle size of superparamagnetic Fe₃O₄ microparticles, *Chem. Mater.*, 2009, **21**, 5079–5087, DOI: [10.1021/cm901618m](#).
 - 37 G. Xu, M. Du, T. Li, Y. Guan and C. Guo, Facile synthesis of magnetically retrievable Fe₃O₄/BiVO₄/CdS heterojunction composite for enhanced photocatalytic degradation of tetracycline under visible light, *Sep. Purif. Technol.*, 2021, **275**, 119157, DOI: [10.1016/j.seppur.2021.119157](#).
 - 38 O. A. Alani, H. A. Ari, S. O. Alani, N. A. O. Offiong and W. Feng, Visible-light-driven bio-templated magnetic copper oxide composite for heterogeneous photo-Fenton degradation of tetracycline, *Water*, 2021, **13**, 1918, DOI: [10.3390/w13141918](#).
 - 39 Y. Liang, W. Xu, J. Fang, Z. Liu, D. Chen, T. Pan, Y. Yu and Z. Fang, Highly dispersed bismuth oxide quantum dots/graphite carbon nitride nanosheets heterojunctions for visible light photocatalytic redox degradation of environmental pollutants, *Appl. Catal., B*, 2021, **295**, 120279, DOI: [10.1016/j.apcatb.2021.120279](#).
 - 40 Z. Zhou, Z. Shen, C. Song, M. Li, H. Li and S. Zhan, Boosting the activation of molecular oxygen and the degradation of tetracycline over high loading Ag single atomic catalyst, *Water Res.*, 2021, **201**(52), 117314, DOI: [10.1016/j.watres.2021.117314](#).
 - 41 Y. Jiao, S. Yang, Y. Zhang, X. Ma, Y. Ma, X. Bai, Y. Xing, Y. Gong and C. Yang, Preparation and characterization of GO/TiO₂/Fe₃O₄ photocatalyst, *J. Funct. Mater.*, 2020, **51**(11), 11134–11139, DOI: [10.3969/j.issn.1001-9731.2020.11.019](#).
 - 42 N. Gupta, H. P. Singh and R. K. Sharma, Metal nanoparticles with high catalytic activity in degradation of methyl orange: An electron relay effect, *J. Mol. Catal. A: Chem.*, 2011, **335**(1–2), 248–252, DOI: [10.1016/j.molcata.2010.12.001](#).
 - 43 H. Pei, Q. Jia, R. Guo, T. Zhang, N. Liu and Z. Mo, Flower-like CeO₂/CdS quantum dots heterojunction nanocomposites with high photocatalytic activity for RhB degradation, *Colloids Surf., A*, 2022, **648**, 129256, DOI: [10.1016/j.colsurfa.2022.129256](#).
 - 44 W. Liu and W. Hu, Green fabrication of h-BN/g-C₃N₄ with efficient holes transfer towards highly improved photocatalytic CO₂ reduction and RhB degradation, *Mater. Charact.*, 2022, **191**, 112165, DOI: [10.1016/j.matchar.2022.112165](#).
 - 45 S. Sharma, A. Mittal, N. S. Chauhan, S. Saini, J. Yadav, M. Kushwaha, R. Chakraborty, S. Sengupta, K. Kumari and N. Kumar, Mechanistic investigation of RhB photodegradation under low power visible LEDs using a Pd-modified TiO₂/Bi₂O₃ photocatalyst: Experimental and DFT studies, *J. Phys. Chem. Solids*, 2022, **162**, 110510, DOI: [10.1016/j.jpcs.2021.110510](#).

