

Cite this: *Chem. Sci.*, 2019, **10**, 2193

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 16th October 2018  
Accepted 18th December 2018DOI: 10.1039/c8sc04610g  
[rsc.li/chemical-science](http://rsc.li/chemical-science)

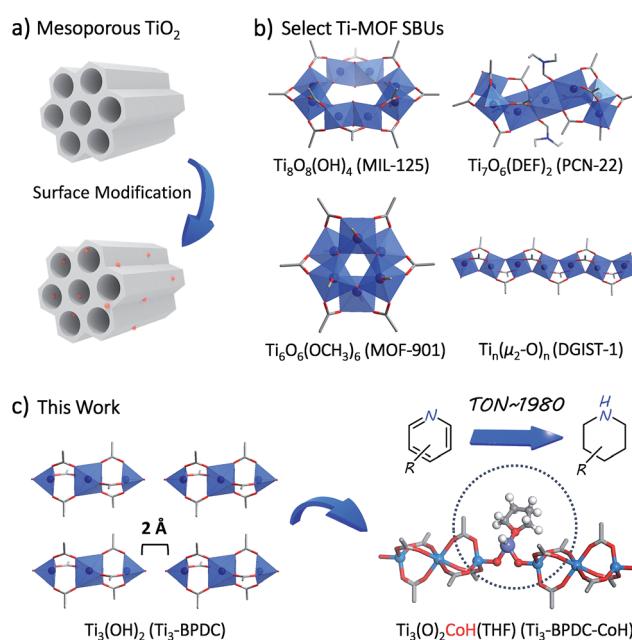
## Introduction

The development and functionalization of Ti-oxo materials is a fertile research area due to their high crust abundance, low toxicity, excellent chemical and thermal stability, and unique photophysical properties. The introduction of permanent porosity into bulk  $\text{TiO}_2$  allows efficient utilization of all surface functionalizable sites to ensure sustainable resource utilization.<sup>1–3</sup> For example, surface modifications of mesoporous titania have generated a series of Ti-OH anchored metal species displaying impressive catalytic or photocatalytic activities.<sup>4–6</sup>

Ti metal-organic frameworks (MOFs) provide a highly tunable platform to realize molecular-level design and construction of single-crystalline and porous Ti-oxo materials that can be further functionalized for catalytic applications.<sup>7–10</sup> However, only a few Ti-carboxylate MOFs have been synthesized and characterized since the report of the first Ti-carboxylate MOF (MIL-125) with  $\text{Ti}_8\text{O}_8(\text{OH})_4$  secondary building units (SBUs) in 2009 (Table S1, ESI†).<sup>11–17</sup> Ti MOFs with permanent porosity, large channels, and sterically open functionalable sites are even rarer.

Herein we report the rational synthesis of a novel porous Ti-carboxylate MOF,  $\text{Ti}_3\text{-BPDC}$  (BPDC = biphenyl-4,4'-dicarboxylate) with unprecedented  $\text{Ti}_3(\text{OH})_2$  SBUs. Two terminal

$\text{Ti}^{\text{IV}}\text{-OH}$  groups in the neighboring SBUs of  $\text{Ti}_3\text{-BPDC}$  point at each other with a 2 Å distance and act as excellent bidentate ligands to complex  $\text{Co}^{\text{II}}$ -hydride species to provide a sterically open and electronically-rich Earth-abundant metal catalyst for the cascade reduction of N-heteroarenes to piperidine and 1,2,3,4-tetrahydroquinoline derivatives (Fig. 1).



<sup>a</sup>Department of Chemistry, University of Chicago, 929 E. 57<sup>th</sup> St., Chicago, Illinois 60637, USA. E-mail: [wenbinlin@uchicago.edu](mailto:wenbinlin@uchicago.edu)

<sup>b</sup>College of Chemistry and Chemical Engineering, iCHEM, State Key Laboratory of Physical Chemistry of Solid Surface, Xiamen University, Xiamen 361005, PR China

† Electronic supplementary information (ESI) available. CCDC 1859034. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c8sc04610g

‡ X. F. and Y. S. contributed equally to this work.

Fig. 1 (a) Surface modification of mesoporous  $\text{TiO}_2$  generates functional materials. (b) Select Ti-MOF SBU structures (MIL-125, PCN-22, MOF-901, and DGIST-1). (c) Schematic illustration of novel  $\text{Ti}_3(\text{OH})_2$  SBUs in  $\text{Ti}_3\text{-BPDC}$  and their metalation to generate anchored  $\text{Co}^{\text{II}}\text{-H}$  species for cascade reduction of N-heteroarenes.



## Results and discussion

### Synthesis and postsynthetic metalation of $\text{Ti}_3\text{-BPDC}$

To prevent the formation of amorphous  $\text{TiO}_2$ , we used  $\text{Ti}_6\text{O}_6(\text{O}^i\text{Pr})_6(\text{abz})_6$  ( $\text{abz} = 4\text{-aminobenzoate}$ ) cluster<sup>18</sup> as the Ti source for MOF growth.<sup>12</sup> Colorless rhombic  $\text{Ti}_3\text{-BPDC}$  crystals were obtained in 31% yield *via* a solvothermal reaction between  $\text{Ti}_6\text{O}_6(\text{O}^i\text{Pr})_6(\text{abz})_6$  and  $\text{H}_2\text{BPDC}$  in *N,N*-dimethylformamide at 120 °C for 3 days with acetic acid (HOAc) as modulator. Single-crystal X-ray diffraction (SXRD) revealed that  $\text{Ti}_3\text{-BPDC}$  crystallizes in the  $R\bar{3}m$  space group. Every three Ti atoms are linked by carboxylate groups to form  $\text{Ti}_3(\text{OH})_2$  SBUs, with the central Ti atom in octahedral coordination with six carboxylate groups and each of the two terminal Ti atoms in tetrahedral coordination with three carboxylate groups and one OH group.  $\text{Ti}_3(\text{OH})_2$  SBUs are connected by six BPDC linkers to afford a 3D framework of *dia* topology with 1D triangle channel of 11 Å in length running along the *c* axis (Fig. 2a). The void space was calculated to be 71.9% by PLATON. Diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS) revealed the presence of  $\nu_{\text{O}-\text{H}}$  stretching band at 3678 cm<sup>-1</sup> for the terminal  $\text{Ti}^{\text{IV}}\text{-OH}$ .<sup>19</sup>

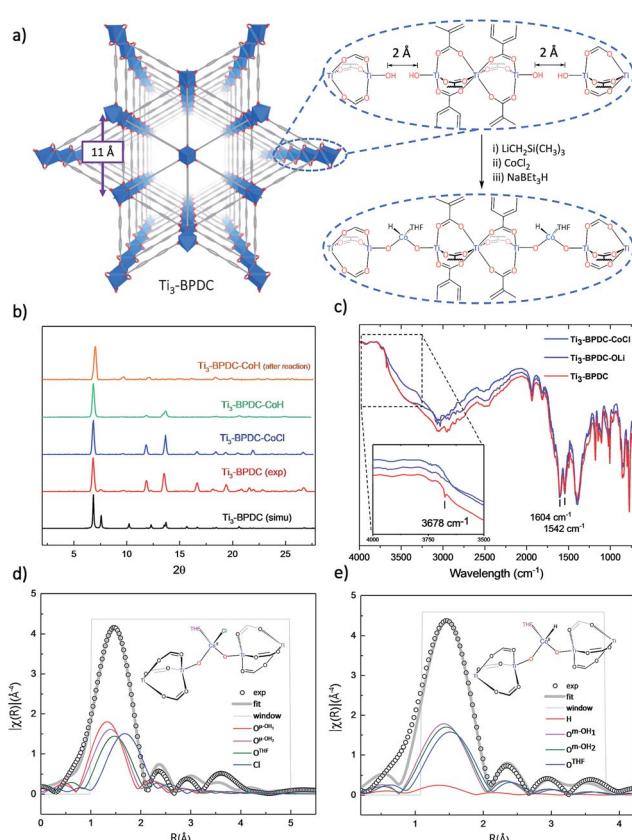


Fig. 2 (a) Structure and SBU arrangement of  $\text{Ti}_3\text{-BPDC}$  and its conversion to  $\text{Ti}_3\text{-BPDC-CoH}$ . (b) PXRD patterns of  $\text{Ti}_3\text{-BPDC}$  (red),  $\text{Ti}_3\text{-BPDC-CoCl}$  (navy), and  $\text{Ti}_3\text{-BPDC-CoH}$  (violet) and after-reaction (orange) along with simulated PXRD based on the SXRD structure (black). (c) DRIFT spectrum of  $\text{Ti}_3\text{-BPDC}$  showing stretching vibration of  $\text{Ti}-\text{OH}$  at 3678 cm<sup>-1</sup> from  $\text{Ti}_3(\text{OH})_2$  SBUs. (d, e) EXAFS spectra (black circles) and fits (grey solid line) in *R*-space at the Co K-edge adsorption of (d)  $\text{Ti}_3\text{-BPDC-CoCl}$  and (e)  $\text{Ti}_3\text{-BPDC-CoH}$ .

<sup>1</sup>H NMR analysis of digested  $\text{Ti}_3\text{-BPDC}$  (in  $\text{D}_3\text{PO}_4/\text{HF}$ ) showed the presence of 1.38 equiv. of HOAc w.r.t.  $\text{H}_2\text{BPDC}$  (Fig. S6, ESI<sup>†</sup>), affording a formula of  $[\text{Ti}_3(\text{BPDC})_3(\text{OH})_2](\text{OAc})_4$ . Powder X-ray diffraction (PXRD) showed that bulk phase and single crystals of  $\text{Ti}_3\text{-BPDC}$  have identical structure (Fig. 2b). Due to relatively stable  $\text{Ti}_3$ -cluster SBUs and strong coordination of carboxylate to  $\text{Ti}^{\text{IV}}$ ,  $\text{Ti}_3\text{-BPDC}$  was thermally stable up to 274 °C (Fig. S7, ESI<sup>†</sup>) and maintained its crystalline structure in a range of organic solvents and bases (Fig. S15, ESI<sup>†</sup>).  $\text{Ti}_3\text{-BPDC}$  exhibits a type I isotherm with a Brunauer–Emmett–Teller (BET) surface area of 636 m<sup>2</sup> g<sup>-1</sup> and a pore size of 11.8 Å. To the best of our knowledge,  $\text{Ti}_3\text{-BPDC}$  is the first Ti-MOF based on the biphenyldicarboxylate ligand, which provides a potential for further functionalization.<sup>20,21</sup>

The unique structure of  $\text{Ti}_3\text{-BPDC}$ , particularly the proximity of the neighboring  $\text{Ti}^{\text{IV}}\text{-OH}$  groups, inspired us to use the SBUs to support Earth-abundant metal catalysts.<sup>22</sup> Although individual SBUs of MOFs have been previously used as structural and functional mimics of metal oxide catalyst supports,<sup>23–28</sup> there has been no study of using neighboring SBUs as bidentate ligands to support Earth-abundant metal catalysts. We posited that chelation by neighboring SBUs affords several advantages including stronger coordination from two or more  $\text{M}-\text{O}^-$  groups, more electron-rich active metal sites, and more sterically open coordination environment around catalytic centers.

$\text{Ti}_3\text{-BPDC}$  was deprotonated with 5 equiv. of  $\text{LiCH}_2\text{Si}(\text{CH}_3)_3$  and then metalated with 1 equiv. of  $\text{CoCl}_2$  in THF to afford  $\text{Ti}_3\text{-BPDC-CoCl}$  as the purple solid. Both the carboxylate groups and linkers remained intact during the lithiation and metalation as evidenced by unchanged carbonyl stretching vibrations in the IR spectra. The disappearance of terminal OH stretching band (Fig. 2c) indicated complete deprotonation of  $\text{Ti}^{\text{IV}}\text{-H}$  groups. Inductively coupled plasma-mass spectrometry (ICP-MS) analysis of digested  $\text{Ti}_3\text{-BPDC-CoCl}$  revealed the presence of  $0.92 \pm 0.04$  Co per  $\text{Ti}_3$  SBU, indicating nearly complete metalation of all  $\text{Ti}-\text{OH}$  pairs. Crystallinity maintained after metalation as evidenced in the PXRD patterns, and SXRD of  $\text{Ti}_3\text{-BPDC-CoCl}$  displayed a nearly identical unit cell parameter to  $\text{Ti}_3\text{-BPDC}$ . Unfortunately, after numerous trials, the coordination environment of Co could not be established through SXRD due to the highly disordered nature of coordinated cobalt atoms. Instead, extended X-ray absorption fine structure (EXAFS) spectroscopy and density functional theory (DFT) were used to determine the Co coordination environment in  $\text{Ti}_3\text{-BPDC-CoCl}$ . DFT calculation at the B3LYP level of theory converged at a distorted tetrahedral  $[(\text{Ti}-\text{O}^-)_2\text{CoCl}(\text{THF})]$  coordination with two oxo groups from the deprotonation of  $\text{Ti}-\text{OH}$  ( $\text{Co}-\text{O}^-$  distances of 1.89 and 1.95 Å), one chloride ion ( $\text{Co}-\text{Cl}$  distance of 2.33 Å), and one THF ( $\text{Co}-\text{O}^{\text{THF}}$  distance of 2.06 Å). The calculated model fitted well to the experimental EXAFS data of  $\text{Ti}_3\text{-BPDC-CoCl}$  (Fig. 2d, Table S5, ESI<sup>†</sup>), which gave  $\text{Co}-(\text{O}^{\text{Ti}})$  distances of 1.86 and 1.93 Å, respectively, with a  $\text{Co}-\text{Cl}$  distance of 2.25 Å and a  $\text{Co}-\text{O}^{\text{THF}}$  distance of 2.03 Å.

Treatment of  $\text{Ti}_3\text{-BPDC-CoCl}$  with 10 equiv. of  $\text{NaBET}_3\text{H}$  in toluene generated  $\text{Ti}_3\text{-BPDC-CoH}$  as a dark blue solid through Cl/H exchange. MOF crystallinity was maintained based on similar PXRD patterns before and after  $\text{NaBET}_3\text{H}$  treatment

(Fig. 2b). 96.5% of chloride was exchanged by hydride as determined by X-ray Fluorescence analysis (Fig. S19, ESI†). X-ray photoelectron spectroscopy (XPS) and X-ray absorption near-edge spectroscopy (XANES) were used to determine the oxidation states of Ti and Co centers in  $\text{Ti}_3\text{-BPDC-CoH}$ . The Co centers exhibited strong  $2p_{3/2}$  and  $2p_{1/2}$  peaks at 781.1 and 796.8 eV along with  $2p_{3/2}$  and  $2p_{1/2}$  shake-up peaks at 785.9 and 802.6 eV, consistent with  $\text{Co}^{\text{II}}$  species (Fig. 3a). Ti centers showed strong  $2p_{3/2}$  and  $2p_{1/2}$  peaks at 458.3 and 464.1 eV, which are characteristic of  $\text{Ti}^{\text{IV}}$  species (Fig. 3b). The Co pre-edge features of  $\text{Ti}_3\text{-BPDC-CoCl}$  and  $\text{Ti}_3\text{-BPDC-CoH}$  are identical to that of  $\text{CoCl}_2$  (Fig. 3c), confirming the  $\text{Co}^{\text{II}}$  oxidation state before and after hydride activation. Similar Ti pre-edge features were observed for  $\text{Ti}_3\text{-BPDC-CoCl}$  and  $\text{Ti}_3\text{-BPDC-CoH}$  (Fig. 3d), indicating the identical Ti oxidation states. Treatment of  $\text{Ti}_3\text{-BPDC-CoH}$  with excess formic acid generated  $0.96 \pm 0.04$  equiv. of  $\text{H}_2$  w.r.t. Co, indicating the presence of Co-H species. EXAFS fitting on  $\text{Ti}_3\text{-BPDC-CoH}$  showed that Co centers adopt  $(\text{Ti}-\text{O}^-)_2\text{Co}$  bridging mode with  $\text{Co}-(\text{O}^{\text{Ti}})$  distances of 1.93 Å and 1.96 Å (Fig. 2e) which are similar to those of  $\text{Ti}_3\text{-BPDC-CoCl}$ . Due to the unique site-isolation effect within MOF structure,<sup>29,30</sup> such monomeric Co-H species with oxo-based chelating ligands cannot be prepared in homogeneous systems due to their tendency to oligomerize.

### Ti-BPDC-CoH catalyzed cascade reduction of pyridines

$\text{Ti}_3\text{-BPDC-CoH}$  displayed high catalytic activities in the cascade reduction of pyridines to piperidine derivatives. As one of the most important building blocks in drugs and bioactive alkaloids,<sup>31,32</sup> the synthesis of piperidines has drawn significant interest in the past few decades. Compared to traditional

ring-closing pathways, catalytic hydrogenation of pyridines provides an atom-/step-efficient strategy to construct piperidines.<sup>33</sup> However, there has been only a few examples of hydrogenation of pyridines using homogeneous Rh<sup>34</sup> and Ir,<sup>35</sup> heterogeneous Rh,<sup>36</sup> Pd,<sup>37</sup> and Co,<sup>38</sup> and metal-free systems,<sup>39</sup> as well as the semi-reduction of pyridines,<sup>40,41</sup> likely due to strong poisoning effect of pyridines on the catalytic sites. Inspired by our previous success in hydroboration and hydrogenation reactions catalyzed by SBU-supported Co-hydrides,<sup>23,42</sup> we envisaged a one-pot cascade reduction pathway to prepare piperidines from pyridines using  $\text{Ti}_3\text{-BPDC-CoH}$ . Pinacolborane (HBpin) was added to the reactions to first dearomatize N-heteroarenes *via* hydroboration, followed by the hydrogenation of the remaining unsaturated bonds of the hydroborated intermediates.

At 0.2 mol%  $\text{Ti}_3\text{-BPDC-CoH}$ , treatment of 3-picoline with 1.05 equiv. of HBpin in *n*-octane under 20 bar  $\text{H}_2$  at 100 °C for 22 h gave 3-methylpiperidine in 97% yield. No obvious change was observed in the MOF's PXRD pattern after catalysis (Fig. 2b), indicating the stability of the MOF framework under reaction condition. Changing *n*-octane to coordinating solvents (e.g., THF) or solvent-free condition led to a dramatic drop in yields (Table S8, ESI†), suggesting the inhibition effect from coordination of the solvent or pyridine substrate. No piperidine product was observed in the absence of MOF, HBpin, or  $\text{H}_2$  (Table S9, ESI†). An unprecedentedly high turnover number (TON) of 1980 was achieved at 0.05 mol% catalyst loading in 3 days. At 0.2–0.5 mol% of Co loading, a wide range of pyridines with electron donating or withdrawing groups on 3-, 4-, or 5-positions of the pyridine rings, were all reduced to piperidines in high yields (73–100%). This cascade reduction reaction also exhibits good functional group tolerance and outstanding product selectivity. Alkoxy, ester, dialkyl amide, and silyl groups all remained intact during the reduction process. For pyridine substrates containing aromatic rings, e.g., 3/4-phenylpyridines and 4-benzylpyridines, the pyridyl rings were selectively reduced without affecting the phenyl rings (Table 1).

Several lines of evidences support the cascade process (Tables 1, S8, Fig. S30†). First, 2-picoline and 2,6-lutidine showed dramatic activity decrease compared to 3-picoline and 3,5-lutidine, respectively, likely due to the blocking of Co coordination by the methyl group(s) to inhibit the hydroboration step. Second, we detected 25% hydroborated 3-picoline by  $\text{Ti}_3\text{-BPDC-CoH}$  in the absence of  $\text{H}_2$ , which demonstrates the Co centers could catalyze the hydroboration step. Third, isolated hydroborated pyridines<sup>41</sup> were quantitatively converted to piperidine at 0.5 mol% of  $\text{Ti}_3\text{-BPDC-CoH}$  under 20 bar  $\text{H}_2$ , while no piperidine was observed without the MOF catalyst. Cascade reduction was thus initiated by dearomatic hydroboration of pyridines followed by hydrogenation of the remaining unsaturated bonds (Fig. 4a). Both steps are catalyzed by the Co-H species.

$\text{Ti}_3\text{-BPDC-CoH}$  was recovered and reused at least 6 times without significant decrease in yields (93–100%, Fig. S32, ESI†). ICP-MS showed minimal leaching of Co and Ti (0.4% and 0.6%, respectively). Hot filtration experiment ruled out the possibility of leached Co species contributing to the cascade reduction

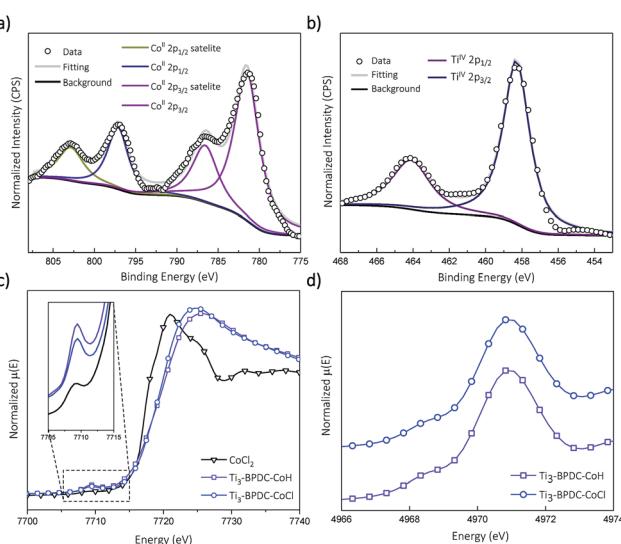


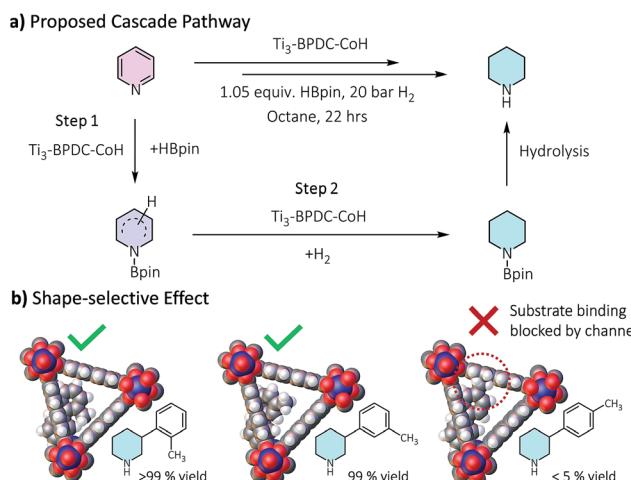
Fig. 3 (a) Co 2p XPS spectra of  $\text{Ti}_3\text{-BPDC-CoH}$  and the fitted result indicates the  $\text{Co}^{2+}$  oxidation state after  $\text{NaBEt}_3\text{H}$  treatment. (b) Ti 2p XPS spectra of  $\text{Ti}_3\text{-BPDC-CoH}$  and the fitted result indicates the  $\text{Ti}^{4+}$  oxidation state after  $\text{NaBEt}_3\text{H}$  treatment. (c) Co pre-edge XANES features of  $\text{Ti}_3\text{-BPDC-CoCl}$  (navy) and  $\text{Ti}_3\text{-BPDC-CoH}$  (violet) in comparison to that of  $\text{CoCl}_2$  (black). (d) Ti pre-edge XANES features of  $\text{Ti}_3\text{-BPDC-CoCl}$  (navy) and  $\text{Ti}_3\text{-BPDC-CoH}$  (violet).



Table 1  $Ti_3$ -BPDC-CoH catalyzed cascade reduction of pyridines<sup>a</sup>

	$Ti_3$ -BPDC-CoH	1.05 equiv. HBpin, 20 bar $H_2$ Octane, 22 hrs		hydrolysis	
<hr/>					
[0.2 mol% Co, 100 °C] 94% yield TON = 470					
[0.2 mol% Co, 100 °C] 97% yield TON = 485					
[0.5 mol% Co, 120 °C] 76% yield TON = 152					
[0.5 mol% Co, 120 °C] 73% yield TON = 146					
[0.5 mol% Co, 140 °C] 92% yield TON = 184					
[0.5 mol% Co, 120 °C] 98% yield TON = 196					
[0.5 mol% Co, 120 °C] 97% yield TON = 194					
[0.5 mol% Co, 120 °C] >99% yield TON = 200					
[0.5 mol% Co, 120 °C] 96% yield TON = 192					
[0.5 mol% Co, 120 °C] 93% yield TON = 186					
[0.5 mol% Co, 100 °C] 73% yield TON = 146					
[0.5 mol% Co, 120 °C] 99% yield TON = 198					
[0.5 mol% Co, 120 °C] 93% yield TON = 186					
[0.5 mol% Co, 120 °C] 0% yield					
[0.5 mol% Co, 120 °C] 0% yield					

<sup>a</sup> 0.50 mmol pyridine, 0.525 mmol HBpin, 20 bar  $H_2$ , 0.2–0.5 mol% of  $Ti_3$ -BPDC-CoH, 100–140 °C, 22 h; yield determined by GC-MS using mesitylene as internal standard. <sup>b</sup> Reaction time: 40 h. <sup>c</sup> 1.05 equiv. HBpin, 35 bar  $H_2$ . <sup>d</sup> 3 equiv. HBpin, 50 bar  $H_2$ . <sup>e</sup> 3 equiv. HBpin, 35 bar  $H_2$ . <sup>f</sup> 3-((Trimethylsilyl)ethynyl)pyridine as substrate, the triple bond was hydrogenated.

Fig. 4 (a) Proposed cascade reduction pathway. (b) Shape selectivity of the cascade reduction of 3-(*m/p/o*-tolyl)pyridine.

reactivity (Fig. S34, ESI†). Additionally, neither Co nanoparticles nor NaBET<sub>3</sub>H afforded any product in the cascade reduction of 3-picoline (Table S10, ESI†). Notably, different regioisomers of 3-tolylpyridines showed remarkable shape selectivity in  $Ti_3$ -BPDC-CoH catalyzed cascade reduction (Fig. 4b). Under the same conditions, 3-(*o*-tolyl)pyridine and 3-(*m*-tolyl)pyridine were completely reduced to piperidines, while most of 3-(*p*-tolyl)pyridine remained unreacted, likely caused by unfavorable steric repulsion between the methyl group of Co-coordinated 3-(*p*-tolyl)pyridine and BPDC ligands from far side of the channel wall (Fig. 4b) to inhibit the hydroboration step.

Table 2  $Ti_3$ -BPDC-CoH catalyzed selective reduction of quinolines<sup>a</sup>

	$Ti_3$ -BPDC-CoH	1.05 equiv. HBpin, 20 bar $H_2$ Octane, 22 h	hydrolysis	
<hr/>				
[0.2 mol% Co, 100 °C] >99% yield (>100:1)				
[0.2 mol% Co, 100 °C] 96% yield (24:1)				
[0.5 mol% Co, 100 °C] >99% yield (pure 1,2,3,4-4HQL)				
[0.5 mol% Co, 100 °C] 98% yield (pure 1,2,3,4-4HQL)				
[0.5 mol% Co, 120 °C] 95% yield (19:1)				
[0.5 mol% Co, 100 °C] 92% yield (11:1)				
[0.5 mol% Co, 140 °C] 98% yield (49:1)				
[0.5 mol% Co, 140 °C] 84% yield (6:1)				
[0.5 mol% Co, 100 °C] 0% yield (N.A.)				

<sup>a</sup> 0.50 mmol quinoline, 0.525 mmol HBpin, 20 bar  $H_2$ , 0.2–0.5 mol% of  $Ti_3$ -BPDC-CoH, 100–140 °C, 22 h; yield determined by GC-MS using mesitylene as internal standard. <sup>b</sup> 1.05 equiv. HBpin, 50 bar  $H_2$ . <sup>c</sup> 3 equiv. HBpin, 20 bar  $H_2$ .

### Ti-BPDC-CoH catalyzed cascade reduction of quinolines

We then applied this cascade protocol to dearomatize other N-heteroarenes. Semi-hydrogenation of quinolines is the most straightforward and convenient way to synthesize 1,2,3,4-tetrahydroquinolines (1,2,3,4-4HQLs), which have broad applications in pharmaceuticals and agrochemicals.<sup>43</sup> Although several catalysts have been reported for such semi-hydrogenation reactions,<sup>44–46</sup> challenges still exist in terms of product selectivity and functional group tolerance.  $Ti_3$ -BPDC-CoH catalyzed semi-hydrogenation of quinolines to generate 1,2,3,4-4HQLs with excellent selectivity and functional group tolerance *via* the cascade reduction process. At 0.2 mol% catalyst loading and 100 °C, 1,2,3,4-4HQL was generated in >99% yield with <1% of 5,6,7,8-4HQL byproduct. Quinolines with methyl groups on different positions (3-,4-,6-,7-) and with different functional groups (Cl, OMe, COOMe) as well as quinoxaline were all semi-hydrogenated to 1,2,3,4-4HQLs in >84% yields and good selectivities (Table 2). No conversion was detected for 2,6-dimethylquinoline due to the inhibition of substrate coordination to the Co center.

### Conclusions

We have synthesized a novel single-crystalline Ti-carboxylate MOF with permanent porosity and large 1D channels based on unique  $Ti_3(OH)_2$  SBUs and BPDC linkers. Each pair of closely spaced  $Ti^{IV}$ -OH groups from neighboring SBUs are deprotonated and then chelate to  $Co^{II}$  centers. Such SBU-supported  $Co^{II}$ -hydride species is highly active for selective cascade reduction of N-heterocyclic rings of pyridines and quinolines: heteroarenes first undergo dearomatative hydroboration followed by hydrogenation of the remaining unsaturated bonds to afford synthetically useful piperidines and 1,2,3,4-tetrahydroquinolines with excellent activity and chemoselectivity. This work expands the applications of MOFs in developing single-site solid catalysts by using neighboring SBUs to support Earth-



abundant metal complexes and highlights the great potential of MOF catalysts in fine chemical synthesis.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by NSF (CHE-1464941). We thank Dr Yuanyuan Zhu, Dr Zekai Lin, and Vlad Kamysbayev for experimental help. XAS analysis was performed at Beamline 10-BM, supported by the Materials Research Collaborative Access Team (MRCAT). Use of the Advanced Photon Source, an Office of Science User Facility operated for the U.S. DOE Office of Science by ANL, was supported by the U.S. DOE under Contract No. DE-AC02-06CH11357. Z. Li acknowledges financial support from the China Scholarship Council and the National Science Foundation of China (21671162).

## Notes and references

- 1 R. Zhang, A. A. Elzatahry, S. S. Al-Deyab and D. Zhao, *Nano Today*, 2012, **7**, 344–366.
- 2 W. Zhou and H. Fu, *ChemCatChem*, 2013, **5**, 885–894.
- 3 W. Li, Z. Wu, J. Wang, A. A. Elzatahry and D. Zhao, *Chem. Mater.*, 2014, **26**, 287–298.
- 4 I. X. Green, W. Tang, M. Neurock and J. T. Yates, *Science*, 2011, **333**, 736–739.
- 5 F. Lakadamyali, A. Reynal, M. Kato, J. R. Durrant and E. Reisner, *Chem.-Eur. J.*, 2012, **18**, 15464–15475.
- 6 G. Kennedy, L. R. Baker and G. A. Somorjai, *Angew. Chem., Int. Ed.*, 2014, **53**, 3405–3408.
- 7 C. Serre, J. A. Groves, P. Lightfoot, A. M. Z. Slawin, P. A. Wright, N. Stock, T. Bein, M. Haouas, F. Taulelle and G. Férey, *Chem. Mater.*, 2006, **18**, 1451–1457.
- 8 H. Assi, G. Mouchaham, N. Steunou, T. Devic and C. Serre, *Chem. Soc. Rev.*, 2017, **46**, 3431–3452.
- 9 H. L. Nguyen, *New J. Chem.*, 2017, **41**, 14030–14043.
- 10 S. Yuan, J.-S. Qin, C. T. Lollar and H.-C. Zhou, *ACS Cent. Sci.*, 2018, **4**, 440–450.
- 11 M. Dan-Hardi, C. Serre, T. Frot, L. Rozes, G. Maurin, C. Sanchez and G. Férey, *J. Am. Chem. Soc.*, 2009, **131**, 10857–10859.
- 12 S. Yuan, T.-F. Liu, D. Feng, J. Tian, K. Wang, J. Qin, Q. Zhang, Y.-P. Chen, M. Bosch, L. Zou, S. J. Teat, S. J. Dalgarno and H.-C. Zhou, *Chem. Sci.*, 2015, **6**, 3926–3930.
- 13 J. A. Mason, L. E. Darago, W. W. Lukens and J. R. Long, *Inorg. Chem.*, 2015, **54**, 10096–10104.
- 14 H. L. Nguyen, F. Gándara, H. Furukawa, T. L. H. Doan, K. E. Cordova and O. M. Yaghi, *J. Am. Chem. Soc.*, 2016, **138**, 4330–4333.
- 15 H. L. Nguyen, T. T. Vu, D. Le, T. L. H. Doan, V. Q. Nguyen and N. T. S. Phan, *ACS Catal.*, 2017, **7**, 338–342.
- 16 S. Wang, T. Kitao, N. Guillou, M. Wahiduzzaman, C. Martineau-Corcos, F. Nouar, A. Tissot, L. Binet, N. Ramsahye, S. Devautour-Vinot, S. Kitagawa, S. Seki, Y. Tsutsui, V. Briois, N. Steunou, G. Maurin, T. Uemura and C. Serre, *Nat. Commun.*, 2018, **9**, 1660.
- 17 Y. Keum, S. Park, Y.-P. Chen and J. Park, *Angew. Chem., Int. Ed.*, 2018, **57**, 14852.
- 18 K. Hong and H. Chun, *Inorg. Chem.*, 2013, **52**, 9705–9707.
- 19 N.-Y. Topsøe, *J. Catal.*, 1991, **128**, 499–511.
- 20 D. Sun, Y. Gao, J. Fu, X. Zeng, Z. Chen and Z. Li, *Chem. Commun.*, 2015, **51**, 2645–2648.
- 21 D. Kim, D. R. Whang and S. Y. Park, *J. Am. Chem. Soc.*, 2016, **138**, 8698–8701.
- 22 J. Liu, L. Chen, H. Cui, J. Zhang, L. Zhang and C.-Y. Su, *Chem. Soc. Rev.*, 2014, **43**, 6011–6061.
- 23 K. Manna, P. Ji, Z. Lin, F. X. Greene, A. Urban, N. C. Thacker and W. Lin, *Nat. Commun.*, 2016, **7**, 12610.
- 24 P. Ji, Y. Song, T. Drake, S. S. Veroneau, Z. Lin, X. Pan and W. Lin, *J. Am. Chem. Soc.*, 2018, **140**, 433–440.
- 25 I. S. Kim, Z. Li, J. Zheng, A. E. Platero-Prats, A. Mavrandakis, S. Pellizzeri, M. Ferrandon, A. Vjunov, L. C. Gallington, T. E. Webber, N. A. Vermeulen, R. L. Penn, R. B. Getman, C. J. Cramer, K. W. Chapman, D. M. Camaioni, J. L. Fulton, J. A. Lercher, O. K. Farha, J. T. Hupp and A. B. F. Martinson, *Angew. Chem., Int. Ed.*, 2018, **57**, 909–913.
- 26 S. Hermes, M.-K. Schröter, R. Schmid, L. Khodeir, M. Muhler, A. Tissler, R. W. Fischer and R. A. Fischer, *Angew. Chem., Int. Ed.*, 2005, **44**, 6237–6241.
- 27 H. G. T. Nguyen, N. M. Schweitzer, C.-Y. Chang, T. L. Drake, M. C. So, P. C. Stair, O. K. Farha, J. T. Hupp and S. T. Nguyen, *ACS Catal.*, 2014, **4**, 2496–2500.
- 28 P. J. Larson, J. L. Cheney, A. D. French, D. M. Klein, B. J. Wylie and A. F. Cozzolino, *Inorg. Chem.*, 2018, **57**, 6825–6832.
- 29 T. Zhang, K. Manna and W. Lin, *J. Am. Chem. Soc.*, 2016, **138**, 3241–3249.
- 30 Z. Li, T. M. Rayder, L. Luo, J. A. Byers and C.-K. Tsung, *J. Am. Chem. Soc.*, 2018, **140**, 8082–8085.
- 31 S. Källström and R. Leino, *Bioorg. Med. Chem.*, 2008, **16**, 601–635.
- 32 E. Vitaku, D. T. Smith and J. T. Njardarson, *J. Med. Chem.*, 2014, **57**, 10257–10274.
- 33 R. Vardanyan, in *Piperidine-Based Drug Discovery*, ed. R. Vardanyan, Elsevier, 2017, pp. 1–82, DOI: 10.1016/B978-0-12-805157-3.00001-6.
- 34 E. Baralt, S. J. Smith, J. Hurwitz, I. T. Horvath and R. H. Fish, *J. Am. Chem. Soc.*, 1992, **114**, 5187–5196.
- 35 X.-B. Wang, W. Zeng and Y.-G. Zhou, *Tetrahedron Lett.*, 2008, **49**, 4922–4924.
- 36 M. Freifelder, R. M. Robinson and G. R. Stone, *J. Org. Chem.*, 1962, **27**, 284–286.
- 37 F. Glorius, N. Spielkamp, S. Holle, R. Goddard and C. W. Lehmann, *Angew. Chem., Int. Ed.*, 2004, **43**, 2850–2852.
- 38 F. Chen, W. Li, B. Sahoo, C. Kreyenschulte, G. Agostini, H. Lund, K. Junge and M. Beller, *Angew. Chem., Int. Ed.*, 2018, **57**, 14488.
- 39 Z.-Y. Liu, Z.-H. Wen and X.-C. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 5817–5820.



40 A. S. Dudnik, V. L. Weidner, A. Motta, M. Delferro and T. J. Marks, *Nat. Chem.*, 2014, **6**, 1100.

41 P. Ji, X. Feng, S. S. Veroneau, Y. Song and W. Lin, *J. Am. Chem. Soc.*, 2017, **139**, 15600–15603.

42 P. Ji, K. Manna, Z. Lin, X. Feng, A. Urban, Y. Song and W. Lin, *J. Am. Chem. Soc.*, 2017, **139**, 7004–7011.

43 V. Sridharan, P. A. Suryavanshi and J. C. Menéndez, *Chem. Rev.*, 2011, **111**, 7157–7259.

44 N. A. Beckers, S. Huynh, X. Zhang, E. J. Luber and J. M. Buriak, *ACS Catal.*, 2012, **2**, 1524–1534.

45 F. Chen, A.-E. Surkus, L. He, M.-M. Pohl, J. Radnik, C. Topf, K. Junge and M. Beller, *J. Am. Chem. Soc.*, 2015, **137**, 11718–11724.

46 I. Sorribes, L. Liu, A. Doménech-Carbó and A. Corma, *ACS Catal.*, 2018, **8**, 4545–4557.

