



INORGANIC CHEMISTRY

FRONTIERS





RESEARCH ARTICLE



Cite this: *Inorg. Chem. Front.*, 2016, **3**, 1527

A microporous Cu²⁺ MOF based on a pyridyl isophthalic acid Schiff base ligand with high CO₂ uptake†‡

Andreas Kourtellis,^a Eleni E. Moushi,^a Ioannis Spanopoulos,^b Christos Tampaxis,^{b,c} Georgia Charalambopoulou,^c Theodore A. Steriotis,^c Giannis S. Papaefstathiou,^d Pantelis N. Trikalitis^b and Anastasios J. Tasiopoulos^{*a}

A new Cu²⁺ complex that was isolated from the initial use of 5-((pyridin-4-ylmethylene)amino)isophthalic acid (PEIPH₂) in 3d metal–organic framework (MOF) chemistry is reported. Complex [(Cu₃(PEIP)₂(5-NH₂-mBDC)(DMF)]_∞·7DMF denoted as **Cu-PEIP**·7DMF was isolated from the reaction of Cu(NO₃)₂·2.5H₂O with PEIPH₂ in *N,N*-dimethylformamide (DMF) at 100 °C and contains both the PEIP²⁻ ligand and its 5-NH₂-mBDC²⁻ fragment. After the structure and properties of **Cu-PEIP** were known an analogous complex was prepared by a rational synthetic method that involved the reaction of Cu(NO₃)₂·2.5H₂O, 5-((pyridin-4-ylmethyl)amino)isophthalic acid (PIPH₂ – the reduced analogue of PEIPH₂) and 5-NH₂-mBDCH₂ in DMF at 100 °C. **Cu-PEIP** comprises two paddle-wheel [Cu₂(COO)₄] units and exhibits a 3D-framework with a unique trinodal underlying network and point symbol (4.5²)₄(4²·5⁴·6⁴·8³·9²)₂(5²·8⁴). This network consists of pillared **kgm-a** layers containing a hexagonal shaped cavity with a relatively large diameter of ~8–9 Å surrounded by six trigonal shaped ones with a smaller diameter of ~4–5 Å and thus resembles the structure of HKUST-1. Gas sorption studies revealed that **Cu-PEIP** exhibits a 1785 m² g⁻¹ BET area as well as high CO₂ sorption capacity (4.75 mmol g⁻¹ at 273 K) and CO₂/CH₄ selectivity (8.5 at zero coverage and 273 K).

Received 25th July 2016,
Accepted 20th September 2016
DOI: 10.1039/c6qi00273k

rsc.li/frontiers-inorganic

Introduction

Metal–organic frameworks (MOFs) have attracted tremendous interest in the last decade due to their unique structural features¹ and potential applications in gas storage, separation,^{2,3} magnetism,⁴ catalysis,⁵ sensing⁶ and so on. The key factor for the discovery of MOFs with novel structural features and potentially interesting physical properties is the development of new synthetic strategies. Appropriate organic ligands are very important in this context, since even small changes in the flexibility, length, or symmetry of the ligands can result in a remarkable diversity of architectures and functions.^{7,8} Although several

elements of rational design have been introduced in MOF chemistry,⁹ exploratory synthetic methods are still a fruitful source of novel materials with interesting properties.¹⁰

An apparent strategy toward new MOFs with interesting properties consists of the use of N- and O-donor polytopic organic ligands.^{8a} Specifically, pyridyl-carboxylates have been confirmed as excellent ligands to assemble multidimensional coordination polymers due to the ability of the N donor atoms to bind most of the metal ions and the high bridging capability of the carboxylate groups. As a result, the carboxylate ligands can bridge several metal ions to form stable oligonuclear or polynuclear secondary building units (SBUs) which are linked through carboxylate or pyridyl N groups to afford multidimensional coordination polymers.^{8a,11} One type of pyridyl polycarboxylate linkers that have attracted significant attention are the tritopic ones consisting of pyridyl and isophthalic acid moieties (for some examples see Scheme 1 in the ESI[†]).^{12–14} When ligands possessing the isophthalic acid moiety are employed in Cu²⁺ chemistry, they often afford structures which are similar to that of HKUST-1 with a **tbo** topology.¹⁵ These structures either contain a layer with the **kgm-a** (augmented kagomé) or the **sql-a** (augmented square lattice) topology that are present in HKUST-1 or display an overall **tbo** topology,^{12d,e,16} since the latter (**tbo**) can be regarded either as a pillared **kgm** or

^aDepartment of Chemistry, University of Cyprus, 1678 Nicosia, Cyprus.
E-mail: atasio@ucy.ac.cy; Fax: +357 22895451; Tel: +357 22892765

^bDepartment of Chemistry, University of Crete, Voutes 71003, Heraklion, Greece
^cNational Center for Scientific Research Demokritos, 15341 Agia Paraskevi Attikis, Greece

^dLaboratory of Inorganic Chemistry, Department of Chemistry, National and Kapodistrian University of Athens, Panepistimiopolis Zografou 157 71, Greece

†Dedicated to Professor Mercouri G. Kanatzidis on the occasion of his 60th birthday.

‡Electronic supplementary information (ESI) available: Structural figures, PXRD, IR, TGA and additional gas-sorption data. CCDC 1492970. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c6qi00273k



pillared **sql** network. Thus, such ligands clearly have the potential to lead in materials resembling the structure and possibly the sorption properties of HKUST-1 and for this reason they have attracted intense interest.^{12–14,16} MOFs with the **tbo** topology are highly desirable for gas sorption applications since: (a) interpenetration is not allowed and therefore high surface areas are often obtained, (b) a relatively high density of open metal sites is created, leading to high gas uptake and (c) the structure contains additional strongly interacting sites (pockets and windows) that increase the overall gas uptake.^{16a}

We are interested in the use of Schiff base ligands containing the isophthalic acid group for the construction of new functional MOFs. In fact we have reported a series of MOFs based on the CIPH₃ ligand (CIPH₃ = 5-(4-carboxybenzylidene-amino)isophthalic acid) with interesting single-crystal-to-single-crystal (SCSC) transformation and sorption properties.^{9c,17} This ligand is more elongated than other commonly used tri-carboxylic acids (such as trimesic acid) and possesses the semi-rigid C=N moiety that introduces into the isolated compounds some but not unlimited flexibility. For all these reasons CIPH₃ was proven capable to afford MOFs with interesting properties. As an extension of this work we employed in MOF chemistry the ligand 5-((pyridin-4-ylmethylene)amino)isophthalic acid (PEIPH₂) (Scheme 1 in the ESI†) that is similar to CIPH₃ but contains a pyridyl group in place of the benzoic acid moiety. This ligand carries all the advantages of the other pyridyl-isophthalic acid linkers mentioned above and displays unpredictable behavior when it is involved in reactions with metal ion sources. This arises from the fact that both PEIPH₂ and its constituent moieties are present in the solution containing the ligand and thus it is possible for them to appear in the resulting compounds giving rise to a variety of new products. Surprisingly the coordination chemistry of PEIPH₂ is actually unexplored with the only known compounds with this ligand being some organotin MOFs.¹⁴

We herein report a new Cu²⁺ MOF $\{[Cu_3(PEIP)_2(5-NH_2-mBDC)(DMF)] \cdot 7DMF\}_\infty$ denoted as **Cu-PEIP-7DMF** which represents the initial 3d metal complex with the ligand PEIPH₂. Although this compound was prepared by a serendipitous self-assembly synthetic procedure, after its structure was known the synthesis of an analogous complex was targeted with high priority and achieved following a rational synthetic method. **Cu-PEIP** exhibits a 3D-framework with a unique trinodal underlying network and point symbol $(4 \cdot 5^2)_4(4^2 \cdot 5^4 \cdot 6^4 \cdot 8^3 \cdot 9^2)_2(5^2 \cdot 8^4)$. This network consists of pillared **kgm-a** layers and thus resembles the structure of HKUST-1. **Cu-PEIP** shows a significant BET area (1785 m² g⁻¹) as well as high CO₂ sorption capacity (4.75 mmol g⁻¹ at 273 K) and CO₂/CH₄ selectivity (8.5 at zero coverage and 273 K).

Experimental

Materials

Reagent grade chemicals were obtained from Aldrich and used without further purification. Water was distilled in-house.

PEIPH₂ and PIPH₂ were synthesized according to the reported literature.^{13d,14}

Synthesis of Cu-PEIP

Method A: PEIPH₂ (0.08 g, 0.296 mmol) was dissolved (after sonication for 3 minutes) in 5 mL *N,N*-dimethylformamide (DMF) in a 20 mL glass vial and solid Cu(NO₃)₂·2.5H₂O (0.08 g, 0.344 mmol) was added to this solution. The mixture was sonicated for 3 min, sealed and then, heated without stirring at 100 °C for 24 h. During this period, green polyhedral-like crystals of **Cu-PEIP** were formed. They were isolated by filtration, washed several times with DMF and diethylether, and dried under vacuum. The yield was 70%. Elemental analysis: Anal. Calc. for C₆₀H₇₇O₂₀N₁₃Cu₃ (**Cu-PEIP-7DMF**) C 48.34, H 5.21, N 12.21, Found: C 48.23, H 5.11, N 12.09.

Method B: Method A was repeated, using 5-NH₂-mBDCH₂ (0.08 g, 0.442 mmol) and 4-pyridinecarboxaldehyde (43 μL, 0.456 mmol) instead of PEIPH₂. The yield was ~65%.

Synthesis of Cu-PIP

PIPH₂ (0.08 g, 0.294 mmol) and 5-NH₂-mBDCH₂ (0.05 g, 0.276 mmol) were dissolved (after sonication for 3 minutes) in DMF (5 mL) in a 20 mL glass vial and solid Cu(NO₃)₂·2.5H₂O (0.08 g, 0.344 mmol) was added to this solution. The mixture was sonicated for 3 min, sealed and then, heated without stirring at 100 °C for 24 h. During this period, green crystalline solid of **Cu-PIP** was formed. The microcrystalline solid was isolated by filtration, washed several times with DMF and diethylether, and dried under vacuum. The yield was 46%. Anal. Calc. for C₆₀H₈₁O₂₀N₁₃Cu₃ (**Cu-PIP-7DMF**) C 48.20, H 5.46, N 12.18, Found: C 47.94, H 5.36, N 12.03.

Physical measurements

Elemental analysis (C, H, N) was performed by the in-house facilities of the University of Cyprus, Chemistry Department. IR spectra were recorded on KBr pellets in the 4000–400 cm⁻¹ range using a Shimadzu Prestige -21 spectrometer. PXRD patterns were recorded on a Shimadzu 6000 Series X-ray diffractometer (Cu Kα radiation, λ = 1.5418 Å). Thermal stability studies were performed with a Shimadzu TGA 50 thermogravimetric analyzer.

Gas sorption measurements

Low-pressure argon, hydrogen, carbon dioxide and methane adsorption measurements were carried out on an Autosorb 1-MP instrument from Quantachrome equipped with multiple pressure transducers for highly accurate analyses and an oil-free vacuum system. High pressure excess adsorption measurements were conducted manometrically on a PCTPro-2000 instrument (Setaram) with the aid of a regular valve sealed stainless-steel measuring cell. The NIST database was implemented for estimating the compressibility of gases (H₂, CH₄, CO₂) and helium was used for dead volume calibrations at 273–303 K. In order to avoid potential helium sorption errors, the dead volume at 77 K was calculated through a reference curve obtained by using different volumes



reaction of $\text{Cu}(\text{NO}_3)_2 \cdot 2.5\text{H}_2\text{O}$, PIPH_2 and $5\text{-NH}_2\text{-mBDC}_2$ in DMF at 100°C in 46% yield. The identity and purity of the bulk products of **Cu-PEIP** and **Cu-PIP** and their structural relation were confirmed by PXRD, elemental analysis and infrared spectroscopy (Fig. S1–S4 in the ESI†).

Compound **Cu-PEIP** crystallizes in the monoclinic space group $I2/m$. There are two crystallographically unique Cu^{2+} ions in the structure (Cu1 and Cu2), both adopting a square pyramidal coordination geometry (Fig. 1): Cu1 is coordinated with four carboxylic oxygen atoms $2 \times (\text{O1-O2})$ of four different PEIP^{2-} ligands and one terminal DMF (O7) solvent molecule, whereas Cu2 is connected with two carboxylate oxygen atoms (O3–O4) from two different PEIP^{2-} anions, two carboxylate oxygen atoms (O5–O6) from two different $5\text{-NH}_2\text{-mBDC}^{2-}$ ligands and one nitrogen atom from a third PEIP^{2-} ligand (N1). This connectivity gives rise to a 3-D framework, which comprises two paddle-wheel $[\text{Cu}_2(\text{COO})_4]$ SBUs and exhibits large channels running mainly along the a -axis (Fig. 2a). The first type of dinuclear SBU, $[\text{Cu}_2]_A$, is formed by two symmetry-equivalent Cu1 metal ions, which are bridged by four *syn,syn*- $\mu_2\text{-COO}^-$ groups originating from four PEIP^{2-} ligands, whereas the second paddle-wheel type SBU, $[\text{Cu}_2]_B$, consists of two symmetry-equivalent Cu2 ions, which are bridged by four *syn,syn*- $\mu_2\text{-COO}^-$ groups originating from two PEIP^{2-} and two $5\text{-NH}_2\text{-mBDC}^{2-}$ ligands. The axial positions in $[\text{Cu}_2]_A$ are occupied by two oxygen atoms from two DMF molecules, while those in $[\text{Cu}_2]_B$ by two pyridyl nitrogen atoms from two PEIP^{2-} ligands. The $5\text{-NH}_2\text{-mBDC}^{2-}$ ligands bridge two $[\text{Cu}_2]_B$ SBUs with a $[\text{Cu}_2]_B \cdots [\text{Cu}_2]_B$ separation of ~ 9.3 Å while the isophthalate

moiety of the PEIP^{2-} ligands bridges a $[\text{Cu}_2]_A$ to a $[\text{Cu}_2]_B$ SBU with the $[\text{Cu}_2]_A \cdots [\text{Cu}_2]_B$ separation being ~ 9.2 Å. In this arrangement, the paddle-wheels and the isophthalate moieties of both ligands create an undulated (3-6-3-6) semi-regular plane net (**kgm-a** lattice) parallel to the bc plane (Fig. 2b). This layer contains two types of cavities; a hexagonal shaped with a relatively large diameter of $\sim 8\text{--}9$ Å surrounded by six trigonal shaped ones with a smaller diameter of $\sim 4\text{--}5$ Å as found by PLATON²⁴ (taking into account the van der Waals radii of the atoms). The trigonal shaped cavities are composed of one $[\text{Cu}_2]_A$ and two $[\text{Cu}_2]_B$ SBUs and are filled with the terminal DMF molecules bound to $[\text{Cu}_2]_A$ SBUs. The hexagonal shaped cavities are composed of two $[\text{Cu}_2]_A$ separating two pairs of two $[\text{Cu}_2]_B$ SBUs. The sides of the hexagonal cavities comprise the isophthalate moieties of two approximately parallel $5\text{-NH}_2\text{-mBDC}^{2-}$ ligands separating two adjacent isophthalate moieties of two pairs of PEIP^{2-} ligands.

The **kgm-a** layers are pillared through the pyridyl groups of the PEIP^{2-} ligands giving rise to hexagonal channels running parallel to the a axis (Fig. 2c and d). Since there are only four PEIP^{2-} ligands composing the hexagonal cavities, only four $[\text{Cu}_2]_B$ SBUs act as connection points in the pillaring. The $5\text{-NH}_2\text{-mBDC}^{2-}$ ligands point their amino group toward the hexagonal cavities, thus compartmentalizing the cavities and the hexagonal channels as shown in Fig. 2c and d. Since part of the isophthalate ligands and part of the $[\text{Cu}_2]$ SBUs participate in the pillaring there is enough space left uncovered giving rise to pores through the other two directions of the material. The pores accommodate DMF molecules.

The solvent-accessible volume calculated by PLATON²⁴ is 5241 \AA^3 and corresponds to 66.5% of the unit-cell volume (7877.0 \AA^3). A representation of the voids using the structure visualization program MERCURY²⁵ reveals a continuous and complex 3D pore network, where the large compartmentalized hexagonal cavities communicate through relatively wide channels with a diameter ≥ 4 Å (Fig. 3).

From the topological point of view the $[\text{Cu}_2]_A$ paddle-wheel SBUs possessing two DMF molecules on the Cu1 apical sites serve as 4-coordinated nodes, while the $[\text{Cu}_2]_B$ SBUs possessing two pyridyl N atoms on the apical positions of the Cu2 ions act as 6-c nodes. The PEIP^{2-} ligands bridge a $[\text{Cu}_2]_A$ to a $[\text{Cu}_2]_B$ through the isophthalate moiety and a $[\text{Cu}_2]_B$ through the pyridyl N atom, thus serving as a 3-c node. The $5\text{-NH}_2\text{-mBDC}^{2-}$ ligand simply bridges two $[\text{Cu}_2]_B$ SBUs and therefore is topologically silent (serves as a bridge). In this arrangement a 3,4,6-coordinated trinodal network with the stoichiometry $(3\text{-c})_4(4\text{-c})(6\text{-c})_2$ and point symbol $(4\cdot 5^2)_4(4^2\cdot 5^4\cdot 6^4\cdot 8^3\cdot 9^2)_2[5^2\cdot 8^4]$ forms which is, so far, unique (Fig. S5–S8 in the ESI†). The network adopted by **Cu-PEIP** resembles the **tbo** net adopted by HKUST-1 and the **eea** net.^{12d,e,15,16} All three nets can be considered as pillared **kgm-a** layers. The augmented Kagomé lattice (**kgm-a**) is based on $[\text{Cu}_2(\text{COO})_4]$ SBUs and isophthalate moieties which alternate to create big hexagonal cavities comprising six paddle-wheels and six isophthalate moieties. In **tbo** the **kgm-a** layers are separated (pillared) by the third carboxylate of the trimesic acid while in the **eea** net the layers are

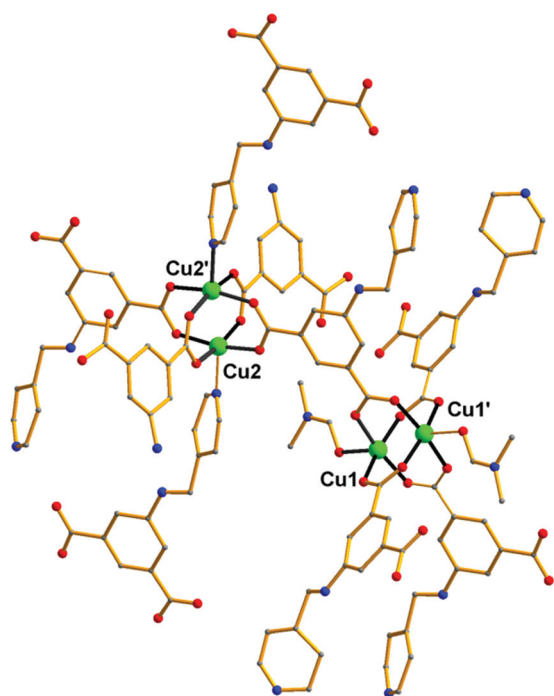


Fig. 1 Representation of the connectivity of the $[\text{Cu}_2^{2+}]_2$ paddle wheel SBUs through the PEIP^{2-} ligand in **Cu-PEIP**. Colour code: Cu green, O red, N blue, C gray. H atoms are omitted for clarity.





Fig. 2 Representations of (a) the 3D framework along the *a* axis, (b) the (3-6-3-6) semi-regular net (augmented Kagomé lattice: *kgm-a*), (c) the compartmentalized hexagonal channels along the *a* axis and (d) the compartmentalized channel projected along the *a* axis for complex **Cu-PEIP**. Colour code: Cu green, O red, N blue, C gray. H atoms are omitted for clarity.



Fig. 3 Representation of the pore network (shown in yellow) of **Cu-PEIP** (only pores and channels with diameter ≥ 4 Å are shown) along the *b* axis.

separated by the pending pyridyl groups of the pyridyl-isophthalate ligands. In both **tbo** and **eea** nets, all six bridging ligands around each hexagonal cavity serve as pillars to both sides of the layer while in **Cu-PEIP** only four PEIP²⁻ ligands serve as pillars since two out of the six bridges around the hexagonal cavities are 5-NH₂-mBDC²⁻ ligands which cannot connect neighboring *kgm-a* layers.

The thermal stability of **Cu-PEIP** and **Cu-PIP** was investigated by means of the thermogravimetric analysis (TGA) technique (Fig. S9 and S10 in the ESI†). The TGA curves for the two complexes are essentially identical and thus only that of **Cu-PEIP** shall be discussed in detail. The TGA curve of **Cu-PEIP** indicates that this compound is decomposed through a multi-

step process which is completed at a fairly low temperature (~ 400 °C). The first two steps that are related to the removal of the lattice and bound DMF solvent molecules appear in the temperature range 30 °C to 260 °C and correspond to $\sim 40\%$ of the material's total mass. This value is in agreement with the corresponding calculated value for **Cu-PEIP**·7DMF ($\sim 39.2\%$). The next steps are associated with the decomposition of the two bridging ligands PEIP²⁻ and 5-NH₂-mBDC²⁻ and are completed at ~ 400 °C.

The relatively large solvent accessible volume present in **Cu-PEIP** prompted us to investigate its gas sorption properties. Several activation methods were employed, however the most efficient one involved the use of dichloromethane to remove the guest solvent molecules followed by treatment with supercritical CO₂. Argon sorption measurements at 87 K revealed a type-I isotherm (Fig. 4), typical for a microporous solid, from which the apparent BET area was found to be 1785 m² g⁻¹ (Langmuir, 1814 m² g⁻¹), close to the geometric surface area (2059 m² g⁻¹) calculated from the single crystal structure using Poreblazer.²⁶ The total pore volume is 0.64 cm³ g⁻¹ at relative pressure, p/p_0 , 0.99, which is slightly lower compared to the value of 0.75 cm³ g⁻¹ calculated²⁶ from the crystal structure. Given that the PXRD pattern of the activated sample suggests an intact framework, the difference in the pore volume could be explained by trapped organic molecules inside the pores of **Cu-PEIP**. The pore size distribution, calculated using Non-



estimated to be 21.2 kJ mol^{-1} and remained nearly constant as a function of the surface coverage (Fig. S13 and S14[†]). Interestingly, this value is higher compared to HKUST-1 (17 kJ mol^{-1}) and among the highest reported for MOFs (Table S1[†]).^{36,37} For example, Ni-MOF-74 with a very high density of open metal sites showed a Q_{st} value of 21.4 kJ mol^{-1} .³⁶ Very recently, a novel MOF without open metal sites, denoted as MAF-38, showed a Q_{st} value of 21.6 kJ mol^{-1} at zero coverage.³⁸ Despite the high Q_{st} value for **Cu-PEIP**, a relatively high CO_2/CH_4 selectivity at low pressures, calculated using the IAST model, is observed reaching 8.5 at 273 K and 8.9 at 298 K.

High-pressure CH_4 measurements revealed that the total gravimetric ($\text{cm}^3 \text{ g}^{-1}$) and volumetric ($\text{cm}^3 \text{ cm}^{-3}$) uptake at 298 K, is 197 and 150 at 35 bar, 233 and 176 at 65 bar and 246 and 187 at 80 bar, respectively. The resulting gravimetric CH_4 working storage capacities in the pressure ranges 5–35 bar (US DOE standard),³⁹ 5–65 bar and 5–80 bar are estimated to be $131 \text{ cm}^3 \text{ g}^{-1}$, $167 \text{ cm}^3 \text{ g}^{-1}$ and $180 \text{ cm}^3 \text{ g}^{-1}$, respectively. The corresponding volumetric working capacities are $99 \text{ cm}^3 \text{ cm}^{-3}$, $125 \text{ cm}^3 \text{ cm}^{-3}$ and $136 \text{ cm}^3 \text{ cm}^{-3}$. These values are lower compared to the best performing MOFs (Tables S1 and S2 in the ESI[†]) due to the combination of high Q_{st} and a moderate surface area in **Cu-PEIP**. Compared to Ni-MOF-74, a MOF with a high Q_{st} for CH_4 and a slightly lower BET area ($1350 \text{ m}^2 \text{ g}^{-1}$), **Cu-PEIP** performs better in terms of the gravimetric working capacity at 5–65 bar (0.110 vs. 0.077 g g^{-1}) and 5–80 bar (0.129 vs. 0.091 g g^{-1}) (Tables S1 and S2 in the ESI[†]).

Low pressure, H_2 sorption isotherms recorded up to 1 bar at 77 K and 87 K revealed an uptake of $206 \text{ cm}^3 \text{ g}^{-1}$ ($2.06 \text{ wt}\%$) and $143 \text{ cm}^3 \text{ g}^{-1}$ ($1.43 \text{ wt}\%$), respectively, which is higher than the benchmark MOF-177 (142 and $82 \text{ cm}^3 \text{ g}^{-1}$) (Fig. S15[†]).⁴⁰ The calculated Q_{st} at zero coverage is 8.74 kJ mol^{-1} (Fig. S16 and S17[†]), which is significantly higher than some well-known and high performance MOFs⁴¹ including MOF-5 and MOF-177 (4.4 kJ mol^{-1}).⁴⁰ High pressure H_2 measurements, revealed an uptake of $614 \text{ cm}^3 \text{ g}^{-1}$ ($5.5 \text{ wt}\%$) which is lower than the ultra-high surface area MOFs such as MOF-210 and NU-100 (Fig. S18[†]). However, at 20 bar, due to a high Q_{st} , the uptake is $4.1 \text{ wt}\%$, comparable to the best performing MOFs.

Conclusions

Summarizing, a new Cu^{2+} MOF is reported that was isolated from the initial use of ligand PEIPH₂ in 3d MOF chemistry. Interestingly, **Cu-PEIP** displays novel structural features although pyridyl isophthalic acid tritopic ligands have been extensively employed in Cu MOF chemistry due to their ability to afford MOFs that display structural similarity with HKUST-1. The unique structural features of **Cu-PEIP** arose from the presence in its structure of both PEIPH₂ and 5-NH₂-mBDCH₂ due to the capability of the tritopic Schiff base ligand to partially decompose in solution and appear in the reaction mixture together with its constituent moieties. After the structure of **Cu-PEIP** was known the synthesis of an analogous compound was targeted and achieved by employing a

rational synthetic procedure. The crystal structure of **Cu-PEIP** exhibits a 3D-framework that contains large pores ($\sim 9 \text{ \AA}$) and solvent accessible volume ($\sim 66.5\%$). In addition, it displays a unique trinodal underlying network consisting of pillared **kgm-a** layers and thus resembles the structure of HKUST-1. Gas sorption studies revealed that **Cu-PEIP** displays a significant BET area of $1785 \text{ m}^2 \text{ g}^{-1}$ and high CO_2 uptake, reaching 4.75 mmol g^{-1} at 273 K and 1 bar (2.80 mmol g^{-1} at 298 K) with good CO_2/CH_4 selectivity (8.5/8.9 at 273 K/298 K). Furthermore, high pressure gas sorption studies revealed that the volumetric CO_2 uptake at 25 bar ($242 \text{ cm}^3 \text{ cm}^{-3}$ at 298 K) is higher compared to representative high surface area MOFs, including MOF-5, MOF-200 and MOF-210. This study emphasizes the usefulness of the elements of serendipity introduced from the employment of polytopic Schiff base ligands in MOF chemistry for the synthesis of microporous MOFs with unique structural features and interesting sorption properties. Further investigations are in progress focusing on the isolation of **Cu-PEIP** analogues containing various functionalized derivatives of isophthalic acid and/or more elongated tritopic pyridyl isophthalic acid ligands.

Acknowledgements

This work was supported by the Cyprus Research Promotion Foundation Grant $\Delta\text{I}\Delta\text{AKT}\Omega\text{P}/0609/43$ which is co-funded by the Republic of Cyprus and the European Regional Development Fund. EM and AJT thank the University of Cyprus for an internal postdoctoral fellowship to EM.

Notes and references

- (a) M. Eddaoudi, D. B. Moler, H. Li, B. Chen, T. M. Reineke, M. O'Keeffe and O. M. Yaghi, *Acc. Chem. Res.*, 2001, **34**, 319–330; (b) D. Bradshaw, J. B. Claridge, E. J. Cussen, T. J. Prior and M. J. Rosseinsky, *Acc. Chem. Res.*, 2005, **38**, 273–282; (c) G. Ferey, *Chem. Soc. Rev.*, 2008, **37**, 191–214.
- (a) N. L. Rosi, J. Eckert, M. Eddaoudi, D. T. Vodak, J. Kim, M. O'Keeffe and O. M. Yaghi, *Science*, 2003, **300**, 1127–1129; (b) S. Zheng, T. Wu, J. Zhang, M. Chow, R. A. Nieto, P. Feng and X. H. Bu, *Angew. Chem., Int. Ed.*, 2010, **49**, 5362–5366; (c) B. F. Abrahams, M. J. Grannas, T. A. Hudson and R. Robson, *Angew. Chem., Int. Ed.*, 2010, **49**, 1087–1089.
- (a) H. Hayashi, A. P. Cote, H. Furukawa, M. O'Keeffe and O. M. Yaghi, *Nat. Mater.*, 2007, **6**, 501–506; (b) R. E. Morris and P. S. Wheatley, *Angew. Chem., Int. Ed.*, 2008, **47**, 4966–4981; (c) S. Noro, S. Kitagawa, M. Kondo and K. Seki, *Angew. Chem., Int. Ed.*, 2000, **39**, 2081–2084.
- (a) E. E. Moushi, T. C. Stamatatos, W. Wernsdorfer, V. Nastopoulos, G. Christou and A. J. Tasiopoulos, *Angew. Chem., Int. Ed.*, 2006, **45**, 7722–7725; (b) P. Dechambenoit and J. R. Long, *Chem. Soc. Rev.*, 2011, **40**, 3249–3265.



- 5 (a) L. Ma, J. M. Falkowski, C. Abney and W. Lin, *Nat. Chem.*, 2010, **2**, 838–846; (b) J.-S. Qin, D.-Y. Du, W. Guan, X.-J. Bo, Y.-F. Li, L.-P. Guo, Z.-M. Su, Y.-Y. Wang, Y.-Q. Lan and H.-C. Zhou, *J. Am. Chem. Soc.*, 2015, **137**, 7169–7177.
- 6 (a) Z. Hu, B. J. Deibert and J. Li, *Chem. Soc. Rev.*, 2014, **43**, 5815–5840; (b) A. Douvali, A. C. Tsipis, S. V. Eliseeva, S. Petoud, G. S. Papaefstathiou, C. D. Malliakas, I. Papadas, G. S. Armatas, I. Margiolaki, M. G. Kanatzidis, T. Lazarides and M. J. Manos, *Angew. Chem., Int. Ed.*, 2015, **54**, 1651–1656.
- 7 (a) O. M. Yaghi, H. Li, C. Davis, D. Richardson and T. L. Groy, *Acc. Chem. Res.*, 1998, **31**, 474–484; (b) M. Eddaoudi, J. Kim, D. Vodak, A. Sudik, J. Wachter, M. O’Keeffe and O. M. Yaghi, *Proc. Natl. Acad. Sci. U. S. A.*, 2002, **99**, 4900–4904.
- 8 (a) X.-L. Zhao and W.-Y. Sun, *CrystEngComm*, 2014, **16**, 3247–3258; (b) B. Manna, A. V. Desai and S. K. Ghosh, *Dalton Trans.*, 2016, **45**, 4060–4072.
- 9 (a) S. M. Cohen, *Chem. Rev.*, 2012, **112**, 970–1000; (b) O. Karagiari, W. Bury, J. E. Mondloch, J. T. Hupp and O. K. Farha, *Angew. Chem., Int. Ed.*, 2014, **53**, 4530–4540; (c) E. J. Kyprianidou, T. Lazarides, S. Kaziannis, C. Kosmidis, G. Itskos, M. J. Manos and A. J. Tasiopoulos, *J. Mater. Chem. A*, 2014, **2**, 5258–5266.
- 10 (a) N. Stock and S. Biswas, *Chem. Rev.*, 2012, **112**, 933–969; (b) Z.-J. Lin, J. Lü, M. Hong and R. Cao, *Chem. Soc. Rev.*, 2014, **43**, 5867–5895.
- 11 (a) C. N. R. Rao, S. Natarajan and R. Vaidhyanathan, *Angew. Chem., Int. Ed.*, 2004, **43**, 1466–1496; (b) E. E. Moushi, A. Kourtellaris, I. Spanopoulos, M. J. Manos, G. S. Papaefstathiou, P. N. Trikalitis and A. J. Tasiopoulos, *Cryst. Growth Des.*, 2015, **15**, 185–193.
- 12 (a) M.-S. Chen, Z.-S. Bai, T. Okamura, Z. Su, S.-S. Chen, W.-Y. Sun and N. Ueyama, *CrystEngComm*, 2010, **12**, 1935–1944; (b) X.-J. Deng, W. Gu, L. Wang, L.-F. Zeng and X. Z. Liu, *Z. Anorg. Allg. Chem.*, 2011, **637**, 708–712; (c) M.-S. Chen, M. Chen, S. Takamizawa, T. Okamura, J. Fan and W.-Y. Sun, *Chem. Commun.*, 2011, **47**, 3787–3789; (d) Y. Xiong, Y.-Z. Fan, R. Yang, S. Chen, M. Pan, J.-J. Jiang and C.-Y. Su, *Chem. Commun.*, 2014, **50**, 14631–14634; (e) Z. Chen, K. Adil, L. J. Weselinski, Y. Belmabkhout and M. Eddaoudi, *J. Mater. Chem. A*, 2015, **3**, 6276–6281.
- 13 (a) X. Zhang, Y.-Y. Huang and Y.-G. Yao, *Inorg. Chem. Commun.*, 2013, **28**, 49–51; (b) L. Qin, J.-S. Hu, L.-F. Huang, Y.-Z. Li, Z.-J. Guo and H.-G. Zheng, *Cryst. Growth Des.*, 2010, **10**, 4176–4183; (c) X. Zhang, J. Cheng, F. Chen, M. Sun and Y. Yao, *Inorg. Chem. Commun.*, 2011, **14**, 358–361; (d) M. C. Das and P. K. Bharadwaj, *J. Am. Chem. Soc.*, 2009, **131**, 10942–10949; (e) M. C. Das and P. K. Bharadwaj, *Chem. – Eur. J.*, 2010, **16**, 5070–5077; (f) A. Karmakar, L. M. D. R. S. Martins, S. Hazra, M. F. C. G. Da Silva and A. J. L. Pombeiro, *Cryst. Growth Des.*, 2016, **16**, 1837–1849; (g) M.-H. Xie, X.-L. Yang and C.-D. Wu, *Chem. – Eur. J.*, 2011, **17**, 11424–11427.
- 14 (a) V. Chandrasekhar, C. Mohapatra and R. Metre, *Cryst. Growth Des.*, 2013, **13**, 4607–4614; (b) V. Chandrasekhar and C. Mohapatra, *Cryst. Growth Des.*, 2013, **13**, 4655–4658.
- 15 S. S.-Y. Chui, S. M.-F. Lo, J. P. H. Charmant, A. G. Orpen and I. D. Williams, *Science*, 1999, **283**, 1148–1150.
- 16 (a) V. Guillermin, D. Kim, J. F. Eubank, R. Luebke, X. Liu, K. Adil, M. S. Lah and M. Eddaoudi, *Chem. Soc. Rev.*, 2014, **43**, 6141–6172; (b) J. F. Eubank, H. Mouttaki, A. J. Cairns, Y. Belmabkhout, L. Wojtas, R. Luebke, M. Alkordi and M. Eddaoudi, *J. Am. Chem. Soc.*, 2011, **133**, 14204–14207; (c) X. Liu, M. Oh and M. S. Lah, *Inorg. Chem.*, 2011, **50**, 5044–5053; (d) X. Liu, M. Oh and M. S. Lah, *Cryst. Growth Des.*, 2011, **11**, 5064–5071; (e) S. Xiang, J. Huang, L. Li, J. Zhang, L. Jiang, X. Kuang and C.-Y. Su, *Inorg. Chem.*, 2011, **50**, 1743–1748; (f) B. Moulton, J. Lu, R. Hajndl, S. Hariharan and M. J. Zaworotko, *Angew. Chem., Int. Ed.*, 2002, **41**, 2821–2824; (g) S. A. Bourne, J. Lu, A. Mondal, B. Moulton and M. J. Zaworotko, *Angew. Chem., Int. Ed.*, 2001, **40**, 2111–2113.
- 17 (a) E. J. Kyprianidou, G. S. Papaefstathiou, M. J. Manos and A. J. Tasiopoulos, *CrystEngComm*, 2012, **14**, 8368–8373; (b) M. J. Manos, E. J. Kyprianidou, G. S. Papaefstathiou and A. J. Tasiopoulos, *Inorg. Chem.*, 2012, **51**, 6308–6314; (c) C. G. Efthymiou, E. J. Kyprianidou, C. J. Milios, M. J. Manos and A. J. Tasiopoulos, *J. Mater. Chem. A*, 2013, **1**, 5061–5069.
- 18 Oxford Diffraction, *CrysAlis CCD and CrysAlis RED*, Oxford Diffraction Ltd., Abingdon, UK, 2008.
- 19 M. C. Burla, R. Caliandro, M. Camalli, B. Carrozzini, G. L. Casciarano, L. De Caro, C. Giacovazzo, G. Polidori and R. Spagna, *J. Appl. Crystallogr.*, 2005, **38**, 381–388.
- 20 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2008, **64**, 112–122.
- 21 L. J. Farrugia, *J. Appl. Crystallogr.*, 1999, **32**, 837–838.
- 22 K. Brandenburg, *DIAMOND, Version 2003.2001d*, Crystal Impact GbR: Bonn, Germany, 2006.
- 23 <http://www.ccp14.ac.uk/ccp/web-mirrors/x-seed/>.
- 24 A. L. Spek, *J. Appl. Crystallogr.*, 2003, **36**, 7–13.
- 25 C. F. Macrae, P. R. Edgington, P. McCabe, E. Pidcock, G. P. Shields, R. Taylor, M. Towler and J. Van De Streek, *J. Appl. Crystallogr.*, 2006, **39**, 453–457.
- 26 L. Sarkisov and A. Harrison, *Mol. Simul.*, 2011, **37**, 1248–1257.
- 27 Y. Lin, C. Kong and L. Chen, *RSC Adv.*, 2016, **6**, 32598–32614.
- 28 Y. Lin, C. Kong and L. Chen, *RSC Adv.*, 2012, **2**, 6417–6419.
- 29 R. Vaidhyanathan, S. S. Iremonger, K. W. Dawson and G. K. H. Shimizu, *Chem. Commun.*, 2009, 5230–5232.
- 30 Y. Fu, D. Sun, Y. Chen, R. Huang, Z. Ding, X. Fu and Z. Li, *Angew. Chem., Int. Ed.*, 2012, **51**, 3364–3367.
- 31 J. Ethiraj, E. Albanese, B. Civalleri, J. G. Vitillo, F. Bonino, S. Chavan, G. C. Shearer, K. P. Lillerud and S. Bordiga, *ChemSusChem*, 2014, **7**, 3382–3388.
- 32 H. Furukawa, N. Ko, Y. B. Go, N. Aratani, S. B. Choi, E. Choi, A. Ö. Yazaydin, R. Q. Snurr, M. O’Keeffe, J. Kim and O. M. Yaghi, *Science*, 2010, **329**, 424–428.



- 33 J. Moellmer, A. Moeller, F. Dreisbach, R. Glaeser and R. Staudt, *Microporous Mesoporous Mater.*, 2011, **138**, 140–148.
- 34 J. M. Simmons, H. Wu, W. Zhou and T. Yildirim, *Energy Environ. Sci.*, 2011, **4**, 2177–2185.
- 35 V. Guillerm, L. J. Weseliński, Y. Belmabkhout, A. J. Cairns, V. D'Elia, L. Wojtas, K. Adil and M. Eddaoudi, *Nat. Chem.*, 2014, **6**, 673–680.
- 36 Y. He, W. Zhou, G. Qian and B. Chen, *Chem. Soc. Rev.*, 2014, **43**, 5657–5678.
- 37 I. Spanopoulos, C. Tsangarakis, E. Klontzas, E. Tylianakis, G. Froudakis, K. Adil, Y. Belmabkhout, M. Eddaoudi and P. N. Trikalitis, *J. Am. Chem. Soc.*, 2016, **138**, 1568–1574.
- 38 J.-M. Lin, C.-T. He, Y. Liu, P.-Q. Liao, D.-D. Zhou, J.-P. Zhang and X.-M. Chen, *Angew. Chem., Int. Ed.*, 2016, **55**, 4674–4678.
- 39 Y. Peng, V. Krungleviciute, I. Eryazici, J. T. Hupp, O. K. Farha and T. Yildirim, *J. Am. Chem. Soc.*, 2013, **135**, 11887–11894.
- 40 H. Furukawa, M. A. Miller and O. M. Yaghi, *J. Mater. Chem.*, 2007, **17**, 3197–3204.
- 41 D. P. Broom, C. J. Webb, K. E. Hurst, P. A. Parilla, T. Gennett, C. M. Brown, R. Zacharia, E. Tylianakis, E. Klontzas, G. E. Froudakis, T. A. Steriotis, P. N. Trikalitis, D. L. Anton, B. Hardy, D. Tamburello, C. Corgnale, B. A. Van Hassel, D. Cossement, R. Chahine and M. Hirscher, *Appl. Phys. A*, 2016, **122**, 151.

